



Cite this: *Nanoscale Adv.*, 2021, **3**, 4799

MoS₂ and CdMoS₄ nanostructure-based UV light photodetectors[†]

Mahendra S. Pawar, ^{ab} Sunil R. Kadam, ^c Bharat B. Kale ^{*c} and Dattatray J. Late ^{ab}

Received 3rd May 2021
Accepted 3rd July 2021

DOI: 10.1039/d1na00326g
rsc.li/nanoscale-advances

We have developed MoS₂ nanosheets and CdMoS₄ hierarchical nanostructures based on a UV light photodetector. The surface morphologies of the as-prepared samples were investigated via field emission scanning electron microscopy (FESEM) and transmission electron microscopy (TEM). The performance parameters for the present photodetectors are investigated under the illumination of UV light having a wavelength of ~385 nm. Upon the illumination of UV light, the CdMoS₄-based photodetector device showed a better response to UV light compared to the MoS₂ device in terms of photoresponsivity, response time (~72 s) and recovery time (~94 s). Our results reveal that CdMoS₄ hierarchical nanostructures are practical for enhancing the device performance.

Introduction

Photodetectors based on nanostructured materials are the significant components in nanoelectronic and optoelectronic devices.^{1–4} Photodetectors with quick photoresponse and high photoresponsivity are in much demand for real-world applications such as optical imaging and communication.^{2,5} To date, photodetectors from numerous nanomaterials (0D, 1D, and 2D) with remarkable response time and high responsivity have been reported to have excitation wavelengths ranging from ultraviolet to near-infrared region.^{6–12} For the development of high-performance photodetectors, semiconducting materials with an appropriate bandgap and nanostructured morphology are highly desirable and important. Although two-dimensional (2D) graphene has attracted significant interest in numerous nanoelectronic systems due to its outstanding electronic, thermal, and mechanical properties, further development has been restricted in optoelectronic devices due to its zero bandgap or semimetallic nature.¹³ In previous reports, researchers have developed a strategy to create a bandgap in graphene and utilized it for broadband photodetector application.¹⁴ However,

the presence of favourable bandgap in other 2D inorganic layered materials such as MoS₂, WS₂, MoSe₂, SnSe₂ and black phosphorous suggests great promise in the fabrication of large scale photodetector devices.^{15–23} These 2D materials also possess a layer-dependent tunable bandgap, *i.e.*, direct bandgap in monolayer and indirect bandgap in the bulk form. It makes these materials a potential candidate in numerous applications such as field effect transistors, solar cells, gas sensors, and energy storage devices.^{24–28} Due to the strong light absorption in the visible to near-infrared region, MoS₂ is widely used in optoelectronic systems. In 2012, Zhang *et al.* reported a single-layer MoS₂ phototransistor for the first time and obtained maximum photoresponsivity of ~7.5 mA W^{−1} at an applied gate voltage (V_g , 50 V).¹² Jason *et al.* reported near-infrared photodetection using bilayer MoS₂, where they have injected hot electrons into MoS₂ in order to originate sub-bandgap photocurrent results into photogain of the order of ~10⁵. This photogain leads to a photoresponsivity of 5.2 A W^{−1} at 1070 nm, which is much higher than that of Si-based photodetectors.²⁹ Also, another report from Zhai *et al.* on monolayer MoS₂ coupled with an organic molecule showed a fast response time of 8 ms and maximum photoresponsivity of ~430 A W^{−1} after Al₂O₃ passivation.³⁰ In addition, reports on MoS₂-based photodetectors show that it reduces the recombination rate of charge carriers along with photoabsorber, thus leading to an increase in the photocurrent.^{31–33} Herein, we report the fabrication of 2D MoS₂ nanosheets and 3D CdMoS₄ nanoflowers based on UV light photodetectors. The solvothermal route was implied for the synthesis of these structures, followed by structural and morphological investigation. We also demonstrated the device performance of these samples under UV light illumination and their cyclic response.

^aPhysical and Material Chemistry Division, CSIR – National Chemical Laboratory, Pune, 411008, Maharashtra, India. E-mail: datta099@gmail.com; djlate@mum. amity.edu

^bAcademy of Scientific and Innovative Research (AcSIR), Ghaziabad 201002, India

^cCentre for Materials for Electronics Technology (C-MET), Department of Electronics and Information and Technology (DeITY), Pune, 411008, Maharashtra, India. E-mail: bbkale@cmet.gov.in

^dCentre for Nanoscience & Nanotechnology, Amity University Maharashtra, Mumbai-Pune Expressway, Bhatan, Post – Somathne, Panvel, Mumbai, Maharashtra 410206, India

[†] Electronic supplementary information (ESI) available. See DOI: 10.1039/d1na00326g



Experimental method

Synthesis of MoS_2 nanosheets

Initially, we dissolved 2 mmol of ammonium molybdate in (40–50 ml) methanol with the help of a stirrer. To this mixture, we added dissolved thiourea in methanol dropwise, followed by stirring for 15 min. The whole solution was then transferred into a Teflon-lined stainless steel autoclave at 150 °C for 48 h. The precipitate was obtained using a Whatman filter paper, followed by washing with ethanol several times and then heated in an oven at 80 °C for 4 h. The MoS_2 powder sample was then annealed at 400 °C for 4 h in an N_2 atmosphere.

Synthesis of CdMoS_4 nanoflowers

For the CdMoS_4 nanoflowers synthesis, we have taken 2 mmol of cadmium nitrate and dissolved it in 40–50 ml methanol. Also, we prepared a 20 ml ammonium molybdate solution by dissolving a ammonium molybdate precursor in methanol with the help of a stirrer and continued for 10 min. To this solution, we added a dissolved cadmium nitrate solution dropwise under constant stirring for 10 min. Next, dissolved thiourea was added dropwise to it, and the solution mixture was stirred further for 15 min. The solution was then transferred into a Teflon-lined stainless steel autoclave at 150 °C for 48 h. After completion of the reaction, the reactor was allowed to cool down to room temperature naturally, followed by washing the product with distilled water and filtered using a Whatman filter paper. The precipitate obtained was washed with ethanol several times and then heated in an oven at 80 °C for 4 h. The CdMoS_4 powder sample was then annealed at 400 °C for 4 h in an N_2 atmosphere.

Both the products were further analysed using numerous microscopy and spectroscopy techniques. The details on the synthesis of MoS_2 nanosheets and CdMoS_4 nanoflowers were reported previously.³⁴

Material characterizations

The structural investigations were carried out *via* X-ray powder diffraction technique (XRD-D8, Advance, Bruker-AXS) and Raman spectrometry (HR-800, Horiba Jobin Yvon, France) at an excitation laser wavelength of 632.8 nm with a power density of $6.37 \times 10^7 \text{ W cm}^{-1}$.² The surface morphologies of the as-prepared samples were characterized using a field emission scanning electron microscope (FESEM, Hitachi, S-4800) and transmission electron microscope (TEM, JEOL, 2010F Instrument).

Device fabrication and electrical measurements

The devices were fabricated on a indium tin oxide (ITO)-coated glass substrate with a source-drain separation of 500 μm . The central region of the conducting surface was etched with the zinc dust and concentrated HCl treatment. Then, we drop-casted our prepared material in this nonconducting region of the ITO substrate. Further, we annealed the device at 200 °C for 8 h in vacuum in order to obtain good adhesion of the as-

prepared material with the glass substrate. The electrical characterizations of the fabricated devices for MoS_2 and CdMoS_4 samples were carried out using a Keithley 2612A source meter, which was connected to a computer through a GPIB 288A interface. All the measurements were done at room temperature.

Results and discussion

XRD of MoS_2 and CdMoS_4

The phase formation of the as-synthesized MoS_2 and CdMoS_4 samples were confirmed by XRD and depicted in Fig. 1(a and b). The XRD patterns of the MoS_2 samples synthesized at 400 °C for 4 h are shown in Fig. 1(a), which match with the JCPDS data card no. 00-009-0312, confirming the formation of a pure hexagonal phase of layered MoS_2 and match well with the earlier report.³⁵ Fig. 1(b) shows the XRD pattern for the CdMoS_4 sample annealed at 400 °C for 4 h. Indexing of the annealed CdMoS_4 sample was carried out using the Powder 4-DICVOLE software, which validated the formation of the monoclinic structure of CdMoS_4 .

Raman spectroscopy of MoS_2 and CdMoS_4

In view of this, the as-prepared samples were characterized *via* Raman spectroscopy and are shown in Fig. 1(c) and (d). The two Raman peaks assigned to the MoS_2 sample correspond to the E_{2g}^1 (in-plane) and A_{1g} (out-of-plane) vibration mode, as shown in Fig. 1(c).

These two Raman modes E_{2g}^1 and A_{1g} appear at 382.5 and 406 cm^{-1} , respectively. The separation of 27.56 cm^{-1} between these two peaks specified the presence of the few-layer nature of MoS_2 . The intense Raman peaks at 125, 150, 182, 238, 285, 307, 398, 664, 754, 819, 860 and 890 cm^{-1} were observed for annealed CdMoS_4 sample shown in Fig. 1(d).

FESEM and TEM of MoS_2

In order to investigate the surface morphology of the as-synthesized MoS_2 and CdMoS_4 samples, FESEM analysis was

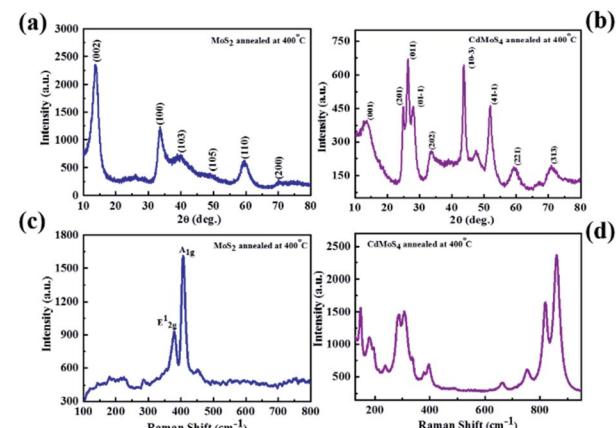


Fig. 1 XRD pattern of (a) MoS_2 and (b) CdMoS_4 samples annealed at 400 °C, Raman spectra of (c) MoS_2 and (d) CdMoS_4 samples annealed at 400 °C.



carried out and the results are depicted in Fig. 2 and 3, respectively. We observed some brake petals of MoS_2 sheets of different sizes located on the long sheet shown in Fig. 2(a and b). The long honeycomb-like sheets measured up to $10\text{ }\mu\text{m}$ and the thickness was found to be $\sim 200\text{ nm}$ (Fig. 2(a and b)). The pore size of the honeycomb sheet is $40\text{--}50\text{ nm}$, and the thickness of the single cell is $\sim 10\text{ nm}$. The TEM image depicted in Fig. 2(c and d) represents the sheet-like structure of MoS_2 and matches well with the FESEM results. The MoS_2 samples were entirely honeycomb-like sheets without aggregation.

XPS of MoS_2

The X-ray photoelectron spectroscopy (XPS) was carried out for MoS_2 sheets, and core-level XPS spectra for Mo 3d and S 2p are shown in Fig. 2(e and f). Fig. 2(e) displays few characteristic peaks corresponding to the orbital of Mo^{2+} , Mo^{4+} and Mo^{6+} observed at $232.29/229.05$, $234.86/231.57$ and $236.07/233.03\text{ eV}$, respectively. In addition, one peak for S 2s is observed at 226.4 eV , which specifies the presence of bridging S^{2-} .³⁶ The two peaks at binding energies of 161.8 eV and 163 eV are detected for S 2p, which can be attributed to $\text{S }2\text{p}_{3/2}$ and $2\text{p}_{1/2}$, respectively, as shown in Fig. 2(f). One minor peak for S at a higher binding energy of 168.52 eV appeared due to surface oxidation of MoS_2 sheets.³⁷

FESEM and TEM of CdMoS_4

The surface morphology of CdMoS_4 samples is shown in Fig. 3(a–c). Fig. 3(a and b) shows the FESEM images that clearly show the formation of a porous nanoflower-like surface

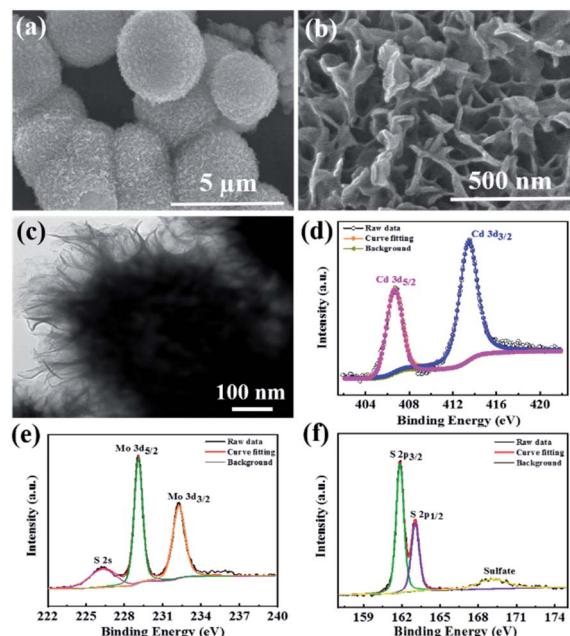


Fig. 3 (a and b) FESEM images, (c) TEM image and (d–f) deconvoluted XPS spectra for Cd 3d, Mo 3d, and S 2p of the CdMoS_4 nanoflowers annealed at $400\text{ }^\circ\text{C}$.

morphology of the CdMoS_4 sample. The average size of the nanoflower was observed to be $\sim 3\text{ }\mu\text{m}$ and thickness $\sim 50\text{ nm}$. This kind of porous nano flower-like structure of CdMoS_4 provides a fair amount of surface area, thus enabling easy transportation of generated electron–hole to the surface and enhancing the photodetector activity. Fig. 3(c) shows the TEM image for the as-prepared CdMoS_4 sample. An original CdMoS_4 nanoflower in Fig. 3(c) shows a marigold flower-like microstructure of $\sim 2\text{ }\mu\text{m}$. The uniform hierarchical nanostructures consist of well-organized independent nano petals with a length of $20\text{--}30\text{ nm}$ (Fig. 3(c)).

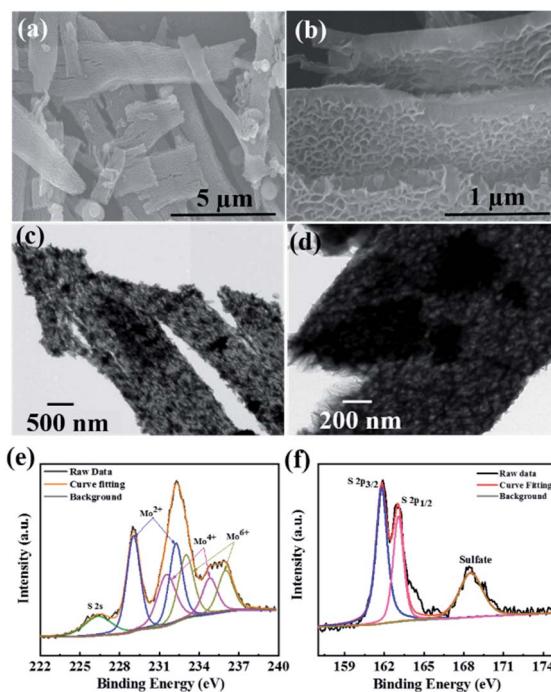


Fig. 2 (a and b) FESEM images, (c and d) TEM images and (e and f) deconvoluted XPS spectra for Mo 3d and S 2p elements of the MoS_2 samples annealed at $400\text{ }^\circ\text{C}$.



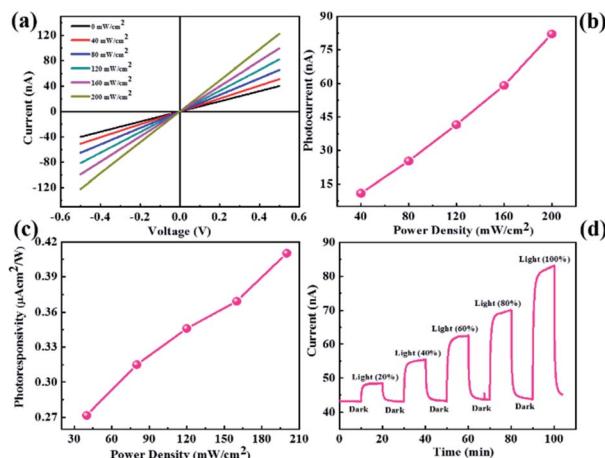


Fig. 4 MoS₂ nanosheet-based photodetector device. (a) current–voltage (I – V) characteristics, (b) photocurrent as a function of power density, (c) photoresponsivity vs. power density and (d) current–time (I – t) plot.

Photoresponse study of MoS₂

The as-synthesized MoS₂ and CdMoS₄ samples were further used for UV light photodetection. The experimental setup used for the measurement of UV light photodetection is shown in ESI Fig. S2.† Fig. 4(a) shows the I – V characteristics of the MoS₂ nanosheet sensor device for numerous power densities under UV light ranging from 0–200 mW cm^{−2}. We observed that the current increases with the increase in the power density of UV light. Photocurrents as a function of the power density plot are shown in Fig. 4(b), which indicates that the photocurrent increases with an increase in the power density. The photocurrent is calculated using the formula shown in eqn (1).

$$I_p = I_{\text{illumination}} - I_{\text{dark}} \quad (1)$$

Fig. 4(c) shows the photoresponsivity vs. power density plot, whereby photoresponsivity is defined as the ratio of photocurrent to power density. We observed that the photoresponsivity increases with the increase in the power density. The photocurrent response of the MoS₂ nanosheet photodetector is shown in Fig. 4(d), which is measured under light illumination and dark conditions at an applied bias voltage of 0.5 V. The response time and recovery time with the MoS₂ nanosheet-based sensor were ~118 s and ~123 s, respectively.

Photoresponse study of CdMoS₄

Similarly, we have performed the UV light photodetector measurements for the CdMoS₄ device shown in Fig. 5. Fig. 5(a) shows the I – V characteristics of the CdMoS₄ nanosheet sensor device at various power densities of UV light ranging from 0–200 mW cm^{−2}. We observed the increment in the current value with the increase in power density. The photocurrent as a function of power density is shown in Fig. 5(b). Upon increasing the power density, the photocurrent also increases. The photoresponsivity vs. power density plot is depicted in Fig. 5(c). The obtained

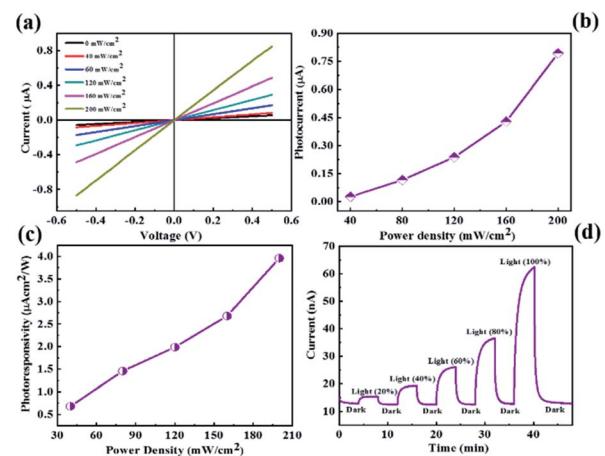


Fig. 5 CdMoS₄ nanoflower-based photodetector device (a) current–voltage (I – V) characteristics, (b) photocurrent as a function of power density, (c) photoresponsivity vs. power density and (d) current–time (I – t) plot.

maximum photoresponsivity was ~4 $\mu\text{A cm}^2 \text{W}^{-1}$ at a power density of 200 mW cm^{−2}, which is much higher than that of the MoS₂-based device. The response time and recovery time for the CdMoS₄-based device are calculated from the I – t plot shown in Fig. 5(d). The values are found to be ~74 s and ~94 s, respectively, which are lower than those of the device fabricated for the MoS₂ nanosheet sample.

The proposed mechanism details under biasing and light illuminations using ITO electrodes, as shown in ESI Fig. S3(a) and (b).† The role of Cd was to produce impurity energy levels into the material, which shifts the absorption edges toward a longer wavelength, resulting in the enhancement in the properties of the photodetector. The enhanced photoexcited carrier density of the CdMoS₄ sample suppressing the electron–hole recombination helps in improving the performance of the photodetector. In addition, the self-assembled nanoflowers from thin petals and the high surface area required for the absorption of light results in a higher number of charge carriers. The electron transfer becomes faster because of the thin petal-like morphology of the CdMoS₄ sample, which also inhibits charge recombination. The comparative photodetector performance of MoS₂ and CdMoS₄ with previously reported Mo-based devices is presented in ESI Table 1.† The cyclic photoresponse study for the annealed MoS₂ and CdMoS₄ samples was carried out for more than 2000 s, and the various cycles have been recorded in light and dark conditions. The current–time (I – t) plots for the MoS₂ and CdMoS₄-based devices are shown in ESI Fig. S4(a) and (b),† respectively. Both the devices displays good photoresponse stability and reproducibility under UV light illumination. The results reveal that the CdMoS₄ device showed good cyclic stability without showing any change in the photocurrent value compared to the MoS₂ device for a long periods.

Conclusion

In conclusion, the structural and morphological investigation of as-synthesized MoS₂ nanosheets and CdMoS₄ nanoflowers



were investigated *via* spectroscopy and microscopy techniques. The UV photodetector devices were fabricated on ITO (indium tin oxide)-coated glass substrates. The CdMoS₄ nanoflowers device showed a better response to UV light compared to pristine MoS₂ nanosheets in terms of photoresponsivity, whereby the response time was 74 s and the recovery time was 94 s. Our results reveal that the device performance of CdMoS₄ materials can be improved by making composite or heterostructures using other 2D materials or by functionalization.

Author contributions

MSP has carried out the experimental work on device fabrication, analysis and first writing of the draft; SRK synthesized the materials and performed the XPS measurements; BBK and DJL supervised the overall work with comments on the first draft, writing, reviewing and editing.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

M. S. Pawar acknowledges CSIR-Delhi [File No: (31/11(1084)/2019-EMR-I)]. Authors thank Director-CSIR-National Chemical laboratory, Pune (India) for the research facilities.

Notes and references

- 1 G. Konstantatos and E. H. Sargent, *Nat. Nanotechnol.*, 2010, **5**, 391.
- 2 A. Pospischil, M. Humer, M. M. Furchi, D. Bachmann, R. Guider, T. Fromherz and T. Mueller, *Nat. Photonics*, 2013, **7**, 892.
- 3 L. Tang, S. E. Kocabas, S. Latif, A. K. Okyay, D. S. Ly-Gagnon, K. C. Saraswat and D. A. Miller, *Nat. Photonics*, 2008, **2**, 226.
- 4 J. S. Jie, W. J. Zhang, Y. Jiang, X. M. Meng, Y. Q. Li and S. T. Lee, *Nano Lett.*, 2006, **6**, 1887.
- 5 T. Mueller, F. Xia and P. Avouris, *Nat. Photonics*, 2010, **4**, 297.
- 6 D. C. Oertel, M. G. Bawendi, A. C. Arango and V. Bulović, *Appl. Phys. Lett.*, 2005, **87**, 213505.
- 7 S. A. McDonald, G. Konstantatos, S. Zhang, P. W. Cyr, E. J. Klem, L. Levina and E. H. Sargent, *Nat. Mater.*, 2005, **4**, 138.
- 8 L. Hu, J. Yan, M. Liao, L. Wu and X. Fang, *Small*, 2011, **7**, 1012.
- 9 C. Lan, C. Li, Y. Yin, H. Guo and S. Wang, *J. Mater. Chem. C*, 2015, **3**, 8074.
- 10 M. S. Pawar, P. K. Bankar, M. A. More and D. J. Late, *RSC Adv.*, 2015, **5**, 88796.
- 11 P. Hu, Z. Wen, L. Wang, P. Tan and K. Xiao, *ACS Nano*, 2012, **6**, 5988.
- 12 Z. Yin, H. Li, H. Li, L. Jiang, Y. Shi, Y. Sun, G. Lu, Q. Zhang, X. Chen and H. Zhang, *ACS Nano*, 2012, **6**, 74.
- 13 I. Meric, M. Y. Han, A. F. Young, B. Ozyilmaz, P. Kim and K. L. Shepard, *Nat. Nanotechnol.*, 2008, **3**, 654.
- 14 Y. Shi, W. Fang, K. Zhang, W. Zhang and L. J. Li, *Small*, 2009, **5**, 2005.
- 15 J. Y. Wu, Y. T. Chun, S. Li, T. Zhang, J. Wang, P. K. Shrestha and D. Chu, *Adv. Mater.*, 2018, **30**, 1705880.
- 16 S. H. Yu, Y. Lee, S. K. Jang, J. Kang, J. Jeon, C. Lee, J. Y. Lee, H. Kim, E. Hwang, S. Lee and J. H. Cho, *ACS Nano*, 2014, **8**, 8285.
- 17 H. Tan, Y. Fan, Y. Zhou, Q. Chen, W. Xu and J. H. Warner, *ACS Nano*, 2016, **10**, 7866.
- 18 N. Perea-López, A. L. Elías, A. Berkdemir, A. Castro-Beltran, H. R. Gutiérrez, S. Feng, R. Lv, T. Hayashi, F. López-Urías, S. Ghosh and B. Muchharla, *Adv. Funct. Mater.*, 2013, **23**, 5511.
- 19 Y. H. Chang, W. Zhang, Y. Zhu, Y. Han, J. Pu, J. K. Chang, W. T. Hsu, J. K. Huang, C. L. Hsu, M. H. Chiu and T. Takenobu, *ACS Nano*, 2014, **8**, 8582.
- 20 W. Zhang, M. H. Chiu, C. H. Chen, W. Chen, L. J. Li and A. T. S. Wee, *ACS Nano*, 2014, **8**, 8653.
- 21 X. Zhou, L. Gan, W. Tian, Q. Zhang, S. Jin, H. Li, Y. Bando, D. Golberg and T. Zhai, *Adv. Mater.*, 2015, **27**, 8035.
- 22 M. Buscema, D. J. Groenendijk, S. I. Blanter, G. A. Steele, H. S. Van Der Zant and A. Castellanos-Gomez, *Nano Lett.*, 2014, **14**, 3347.
- 23 L. Ye, H. Li, Z. Chen and J. Xu, *ACS Photonics*, 2016, **3**, 692.
- 24 C. Guo, Z. Tian, Y. Xiao, Q. Mi and J. Xue, *Appl. Phys. Lett.*, 2016, **109**, 203104.
- 25 M. L. Tsai, S. H. Su, J. K. Chang, D. S. Tsai, C. H. Chen, C. I. Wu, L. J. Li, L. J. Chen and J. H. He, *ACS Nano*, 2014, **8**, 8317.
- 26 D. J. Late, Y. K. Huang, B. Liu, J. Acharya, S. N. Shirodkar, J. Luo, A. Yan, D. Charles, V. Waghmare, V. P. Dravid and C. N. R. Rao, *ACS Nano*, 2013, **7**, 4879.
- 27 C. Hao, B. Yang, F. Wen, J. Xiang, L. Li, W. Wang, Z. Zeng, B. Xu, Z. Zhao, Z. Liu and Y. Tian, *Adv. Mater.*, 2016, **28**, 3194.
- 28 R. Bhandavat, L. David and G. Singh, *J. Phys. Chem. Lett.*, 2012, **3**, 1523.
- 29 W. Wang, A. Klots, D. Prasai, Y. Yang, K. I. Bolotin and J. Valentine, *Nano Lett.*, 2015, **15**, 7440.
- 30 Y. Huang, F. Zhuge, J. Hou, L. Lv, P. Luo, N. Zhou, L. Gan and T. Zhai, *ACS Nano*, 2018, **12**, 4062.
- 31 C. Fang, H. Wang, Z. Shen, H. Shen, S. Wang, J. Ma, J. Wang, H. Luo and D. Li, *ACS Appl. Mater. Interfaces*, 2019, **11**, 8419.
- 32 L. Wang, J. Jie, Z. Shao, Q. Zhang, X. Zhang, Y. Wang, Z. Sun and S. T. Lee, *Adv. Funct. Mater.*, 2015, **25**, 2910.
- 33 W. Zhang, C. P. Chuu, J. K. Huang, C. H. Chen, M. L. Tsai, Y. H. Chang, C. T. Liang, Y. Z. Chen, Y. L. Chueh, J. H. He and M. Y. Chou, *Sci. Rep.*, 2014, **4**, 3826.
- 34 S. R. Kadam, D. J. Late, R. P. Panmand, M. V. Kulkarni, L. K. Nikam, S. W. Gosavi, C. J. Park and B. B. Kale, *J. Mater. Chem. A*, 2015, **3**, 21233.
- 35 X. Zhang, H. Tang, M. Xue and C. Li, *Mater. Lett.*, 2014, **130**, 83.
- 36 C. Wu, D. Liu, H. Li and J. Li, *Small*, 2018, **14**, 1704227.
- 37 N. Karikalalan, R. Karthik, S. M. Chen, C. Karuppiah and A. Elangovan, *Sci. Rep.*, 2017, **7**, 1–10.

