


 Cite this: *RSC Adv.*, 2021, 11, 20268

Size-controlled synthesis of porous ZnSnO₃ nanocubes for improving formaldehyde gas sensitivity

 Jiaoling Zheng,^{†a} Huanhuan Hou,^{†ab} Hao Fu,^{cd} Liping Gao^{id*ac} and Hongjie Liu^{*c}

During the detection of formaldehyde, sensitivity and selectivity is still a challenging issue for most reported gas sensors. Herein, an alternative formaldehyde chemosensor that is based on porous ZnSnO₃ nanocubes was synthesized. The products are characterized by XRD, SEM, TEM (HRTEM), XPS, PL measurements and N₂ adsorption–desorption. The size of the ZnSnO₃ nanocubes is about 100 nm and the corresponding specific surface area is 70.001 m² g⁻¹. A gas sensor based on these porous ZnSnO₃ nanocubes shows high sensitivity and selectivity to formaldehyde. The porous ZnSnO₃ nanocube sensor could detect 50 ppm formaldehyde at about 210 °C with a response value of 21.2, which is twice as much as ethanol, and 3 times that of the other five gases. Moreover, the response of the sensor had an acceptable change after a pulse test for 90 days. The sensor can detect formaldehyde with a minimum concentration of 1 ppm, and it has a good linear relationship between 1–50 ppm formaldehyde. The gas sensor based on porous ZnSnO₃ nanocubes can be utilized as a promising candidate for a practical detector of formaldehyde due to its high gas response and excellent selectivity.

Received 9th March 2021

Accepted 7th May 2021

DOI: 10.1039/d1ra01852c

rsc.li/rsc-advances

1. Introduction

VOC pollutants, such as ethanol, ammonia, acetone, formaldehyde and benzene *etc.*, have attracted extensive attention due to their toxicity to humans and atmospheric pollution.^{1,2} The most concerning among VOCs is formaldehyde due to its carcinogenicity, according to the World Health Organization (WHO), and it is the main pollutant resulting from home decoration.³ The Standardization Administration of the People's Republic of China has regulated the indoor permissible release with a limit of 0.1 ppm,⁴ and the American Conference of Governmental Industrial Hygienists (ACGIH) has recommended a threshold limit value of 0.1 ppm for formaldehyde.⁵ Long term exposure to formaldehyde can cause serious damage to human sensory organs, and can even lead to cancer.⁴ Therefore, real-time and effective formaldehyde monitoring methods are needed to prevent it from exceeding the threshold for danger and thereby affecting human health and causing environmental pollution. There are many common

formaldehyde detection methods, including spectroscopy,⁶ fluorescence,⁷ polarography,⁸ chromatography,⁹ semiconductor gas sensors¹⁰ *etc.* Among these tested methods, semiconductor gas sensors have attracted great attention due to their convenient portability, low power consumption, high sensitivity and good selectivity.

Sensitive materials are the core components of semiconductor gas sensors. Traditional semiconductor sensing materials include ZnO,¹¹ SnO₂,¹² In₂O₃,¹³ WO₃,¹⁴ *etc.* However, a single component usually cannot fulfill all of the requirements such as high response and selectivity, low operation temperature and good stability.¹⁵ Therefore, more and more researchers have committed to developing multi-component materials. As a famous multifunctional material, zinc stannate (ZnSnO₃) has attracted considerable attention due to its potential applications in the fields of photocatalysis,¹⁶ gas sensing,^{17–20} Li-ion batteries,²¹ *etc.* In recent years, the gas-sensing properties of ZnSnO₃ with different morphologies have been studied, such as cubic ZnSnO₃,^{22,23} ZnSnO₃ nanospheres,^{24,25} ZnSnO₃ nanorods,²⁶ *etc.* Among these structural materials, porous materials have attracted great attention due to the improvement of the gas sensitivity of the materials. The inherent reason is that porous structures have large specific surface areas and more reaction sites,^{27,28} which are beneficial for gas diffusion and mass transport,^{29,30} promoting oxygen adsorption, and thereby enhancing the gas response of the materials. For example, the porous NiO nanotetrahedra prepared by Fu *et al.* showed excellent gas-sensing performance toward formaldehyde.³¹ A hierarchical porous LaFeO₃ material

^aSchool of Materials and Chemical Engineering, Chuzhou University, Chuzhou, 239000, China. E-mail: gaozhangping@163.com

^bSchool of Chemistry and Chemical Engineering, Anhui University of Technology, Ma'anshan, 243000, China

^cDepartment of Science and Technology, Shiyuan College of Nanning Normal University, Nanning, 530226, China. E-mail: hongjieliu2008@163.com

^dSchool of Chemistry & Chemical Engineering, Guangxi University, Nanning, 530004, China

[†] These authors contributed equally to this work.


was prepared *via* a low-cost and simple method, which could detect 50 ppb formaldehyde.³² 3D ordered porous SnO₂ with a controllable pore diameter was used with enhanced formaldehyde sensing performance.³³ Therefore, it is a feasible and good approach to synthesize a porous ZnSnO₃ material to detect formaldehyde gas.

In this work, porous ZnSnO₃ nanocubes were synthesized by a facile, template-free hydrothermal method combined with subsequent calcination. The size of the porous ZnSnO₃ nanocubes is 100 nm and the material has a large specific surface area of 70.001 m² g⁻¹. The as-prepared porous ZnSnO₃ nanocube sensor shows excellent gas-sensing properties toward formaldehyde gas. The sensor exhibits a high response (21.2) to 50 ppm of formaldehyde at 210 °C and good selectivity, making it a promising candidate for a practical detector of formaldehyde gas.

2. Experimental section

All of the reagents (analytical-grade purity) were purchased from the Shanghai Chemical Reagent Co. Ltd. (Shanghai, China) and were used without further purification. Deionized water was used throughout the experiments.

2.1. Material synthesis

A typical synthesis procedure of the porous ZnSnO₃ cubes was as follows: 1.0518 g of tin tetrachloride pentahydrate (SnCl₄·5H₂O) and 0.6659 g of zinc acetate (Zn(AC)₂·2H₂O) were dissolved in 20 mL of deionized water under vigorous stirring at room temperature, followed by the addition of 3 M NaOH aqueous solution. Then, the solution was transferred into a Teflon-lined stainless-steel autoclave with a capacity of 80 mL and maintained at 160 °C for 2 h. After cooling down to room temperature, the white precipitate was filtered, washed with distilled water and alcohol 4 times to remove the ions possibly remaining in the final product, and then dried in air at 60 °C for 12 h. Finally, the as-obtained precipitate was calcined at 500 °C with heating rate of 2 °C min⁻¹ in a muffle furnace for 2 h. The synthesis process of the nanocubes is shown in Fig. 1.

2.2. Material characterization

Powder X-ray diffraction measurements were performed with a Bruker D8 ADVANCE X-ray diffractometer in a scanning range of 10–70° (2θ) at a rate of 0.03° (2θ) per s with Cu Kα radiation.

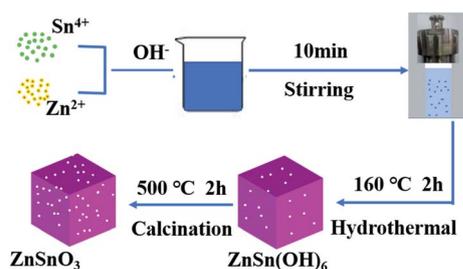


Fig. 1 The synthesis process of the ZnSnO₃ nanocubes.

Field-emission scanning electron microscopy (FESEM) (Hitachi SU5000, Japan) and transmission electron microscopy (TEM) (FEI Tecnai G2 f20 twin, 200 kV) were used to characterize the morphologies of the materials. The decomposition process of the precursors was investigated using a SDT-Q600 thermal analyzer with a heating rate of 10 °C min⁻¹ under N₂ atmosphere. The nitrogen (N₂) adsorption-desorption study was conducted using a Gemini V2380. Brunauer-Emmett-Teller (BET) measurements were used to determine the specific surface area and pore volume. Room temperature PL measurements were performed on a steady state and transient state fluorescence spectrometer (HORIBA TCSPC FluoroLog-3, USA). Elemental and solid surface analyses of the material were performed using X-ray photoelectron spectroscopy (XPS) (Thermo Scientific ESCALAB 250Xi, Al Kα X-ray monochromator).

2.3. Gas response test

The experimental equipment used for the various VOC gas tests in the manuscript is consistent with that of our previous report.³⁴ First of all, the sample and adhesive were fully ground in an agate mortar to form a gas sensing paste. The paste was then coated on the alumina ceramic tube, on which was loaded two Au electrodes and four Pt wires. After drying for 15 min under IR radiation, the alumina ceramic tube was sintered at 500 °C for 2 h, and then welded to the pedestal. Finally, the sensor was aged at 250 °C for 7 days to increase its stability. The gas sensing properties were measured using a WS-30A system (Wei Sheng Instruments Co., Zhengzhou, China) under laboratory conditions. The relative humidity of the test was about 50%. The circuit voltage (V_c) was set at 5 V, and the output voltage (V_{out}) was set as the terminal voltage of the load resistor (R_L). The gas response of the sensor in this paper was defined as $S = R_a/R_g$ (reducing gases) or $S = R_g/R_a$ (oxidizing gases). The response or recovery time was expressed as the time taken for the sensor output to reach 90% of its saturation after applying or switching off the gas in a step function.

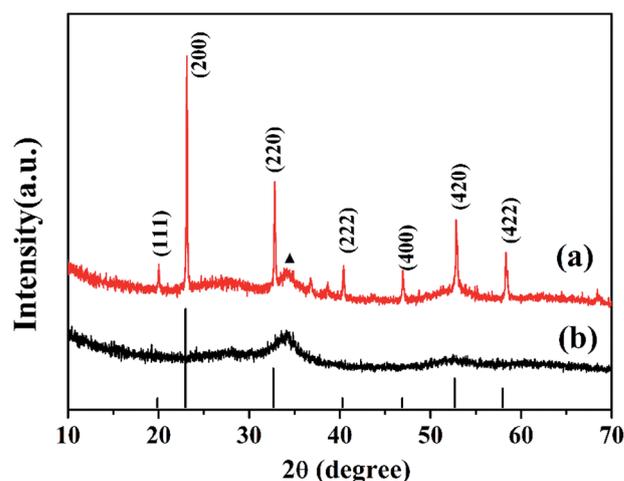


Fig. 2 XRD patterns of the ZnSn(OH)₆ precursor (a) and porous ZnSnO₃ nanocubes (b).

3. Results and discussion

3.1. Material characterization

Fig. 2 shows the XRD patterns of the $\text{ZnSn}(\text{OH})_6$ precursor (Fig. 2a) and porous ZnSnO_3 nanocubes calcined at 500°C (Fig. 2b). From Fig. 2a, the peaks in the XRD pattern can be indexed to the cubic phase of $\text{ZnSn}(\text{OH})_6$ (JCPDS no. 74-1825), which is consistent with the literature reports.³⁵ The strong intensity of the crystallization peaks indicates the good crystallinity of the material. As shown in Fig. 2b, only one broad

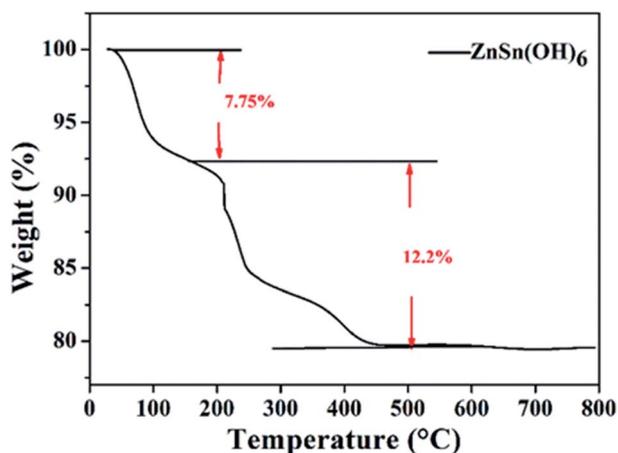


Fig. 3 TG curve of the $\text{ZnSn}(\text{OH})_6$ precursor.

peak can be observed, which is related to amorphous ZnSnO_3 . Through careful observation of the $\text{ZnSn}(\text{OH})_6$ precursor (Fig. 2a), an impurity peak can be seen near the (220) crystal plane, which may be due to the decomposition of the precursor under hydrothermal conditions (high temperature and high pressure), which will be further confirmed by TG analysis.

TG analysis was carried out to examine the conversion process of the precursors during calcination. Fig. 3 shows the TG analysis of the precursor. The weight loss of 7.75% from 40 to 160°C is attributed to the removal of the existing adsorbed water in the precursor. It can be seen from the TG curve that there is a weight loss of 12.2% at high temperatures ($160\text{--}500^\circ\text{C}$), which is attributed to the removal of hydroxyl to generate zinc stannate and water. When the temperature reaches 500°C , the thermogravimetric curve levels off, showing that the zinc stannate product has been completely achieved. The rate of weight loss is 12.2%, which is less than theoretical value (18.88%). The reason is that part of the $\text{ZnSn}(\text{OH})_6$ has decomposed into ZnSnO_3 under the hydrothermal process, which is consistent with the XRD analysis.

The morphology and micro-structure are observed using scanning electronic microscopy (SEM) and transmission electron microscopy (TEM), respectively. From Fig. 4a, it can be seen that the products are uniform nanocubes. Meanwhile, the corresponding element mapping images of ZnSnO_3 are shown in Fig. 4b, demonstrating that the Zn, Sn and O elements are well distributed homogeneously throughout the whole area. The TEM image (Fig. 4c) shows that the products have porous structures,

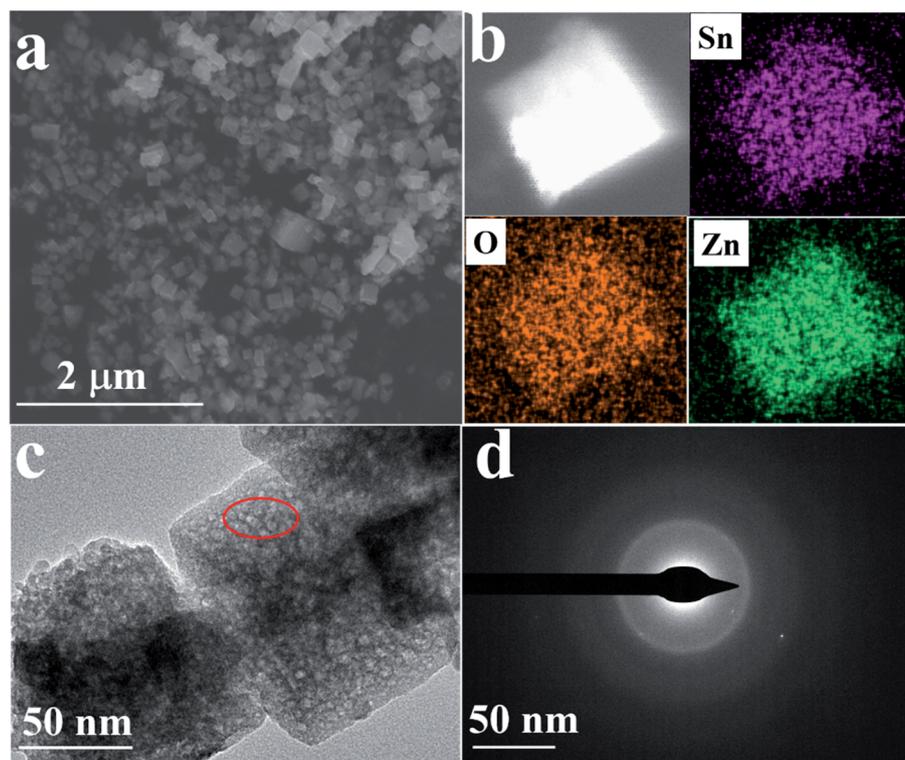


Fig. 4 (a) SEM images and (b) SEM-EDS mapping of the porous ZnSnO_3 nanocubes; (c) TEM and (d) SAED images of the porous ZnSnO_3 nanocubes.



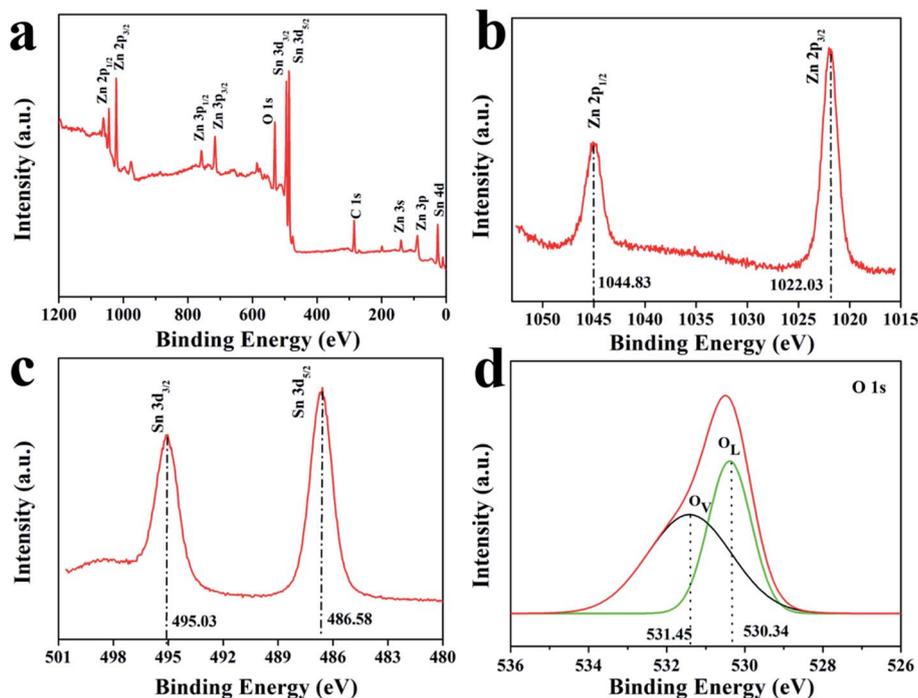


Fig. 5 XPS spectra of the ZnSnO₃ hollow microspheres: (a) survey spectrum, (b) Zn region, (c) Sn region and (d) O region.

which are assembled from tiny nanocrystals. Thermal decomposition of the precursor in air at a high temperature yields porous ZnSnO₃ cubes, which is due to the alkaline (NaOH) etching and the release of H₂O.³⁶ It can be seen from Fig. 4d that the diffraction ring is a dispersion ring, which proves that the material is an amorphous structure, corresponding with the XRD analysis. Due to the ultrafine size and disordered distribution of the ZnSnO₃ nanocrystals, from a macro perspective, the assembled ZnSnO₃ cores behave similarly to an amorphous material and are therefore considered amorphous structures, which are more effective than large crystals in overcoming electrochemical and mechanical degradation.^{37–39}

Surface sensitive X-ray photoelectron spectroscopy (XPS) was conducted to elucidate the chemical composition of the porous ZnSnO₃ nanocubes and the chemical states of Sn, Zn and O in ZnSnO₃. The binding energies obtained from the XPS spectra were calibrated with reference to the signal from C 1s at

284.8 eV. Fig. 5a shows the survey XPS spectrum of the porous ZnSnO₃ nanocubes. This clearly reveals that the obtained product contains Zn, Sn and O elements, as well as C contamination. The two peaks (Fig. 5b) at 1022.03 eV and 1044.83 eV are attributed to Zn 2p_{3/2} and Zn 2p_{1/2} for the Zn²⁺ state, respectively. As shown in Fig. 5c, the peaks located at 486.58 eV and 495.03 eV correspond to Sn 3d_{5/2} and Sn 3d_{3/2} for the Sn⁴⁺ state, respectively. The peak centered at ~530.1 eV belongs to O 1s. From the XPS-peak-differentiating analysis, we could clearly see that there are two separate peaks; one peak at 530.34 eV is determined to be from the lattice oxygen (O_L), while the other one located at ~531.45 eV is attributed to the oxygen vacancies (O_V) (Fig. 5d).

The ZnSnO₃ nanocubes exhibit a porous structure and it is therefore interesting to study the surface area and the pore size of these nanocubes. Fig. 6a shows a typical N₂ adsorption and desorption isotherm for the porous ZnSnO₃ nanocubes. The N₂

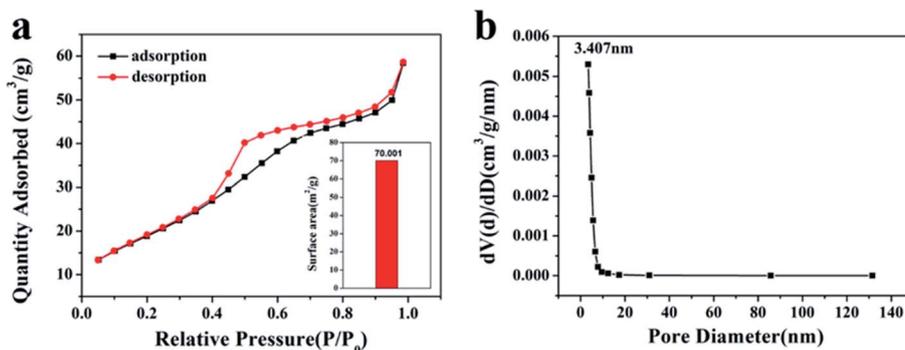


Fig. 6 N₂ adsorption–desorption curves (a) and corresponding pore size distribution curve (b) of the porous ZnSnO₃ nanocubes.



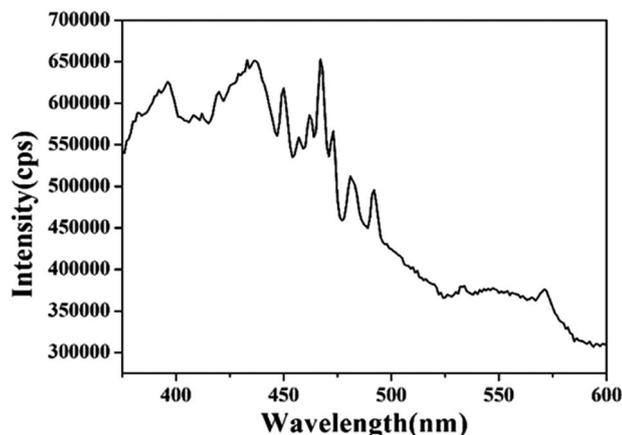


Fig. 7 Photoluminescence spectrum of the ZnSnO₃ nanocubes at room temperature, $\lambda_{\text{ex}} = 325$ nm.

sorption isotherm of the porous ZnSnO₃ nanocubes can be categorized as type IV based on IUPAC classification. The BET surface area of the product was calculated to be 70.001 m² g⁻¹. The corresponding BJH pore size distribution plot (Fig. 6b) of the porous ZnSnO₃ nanocubes shows that the average pore size of this sample is around 3.4 nm, which corresponds with the TEM in Fig. 4c. The results show that the ZnSnO₃ nanocubes have a large specific surface area and abundant interface/microporous structures. A porous structure is conducive to the rapid diffusion of the gas, thereby, improving the gas-sensing properties of porous materials.³⁴

Fig. 7 shows the PL spectrum of the prepared porous ZnSnO₃ nanocubes. The PL spectrum of the porous ZnSnO₃ nanocubes displays a near-band-edge excitonic emission ranging between 360 and 480 nm which is similar to that reported in the literature.⁴⁰ The blue–green light luminescence from the as synthesized porous ZnSnO₃ nanocubes can be attributed to the oxygen-related defects that have been introduced during growth. The emission peak at 394 nm is believed to be due to the oxygen vacancies which can combine with the holes of the valence band to form V_O⁺⁺.⁴¹ The emission peak at 437 nm is attributed to the Sn interstitials.^{42,43} The emission at 446 nm is attributed to the transition from shallow donors (oxygen vacancies) to the valence band.^{43,44} The existence of oxygen vacancies promotes the formation of adsorbed oxygen,⁴⁵ which in turn promotes the reaction of the gas and the adsorbed oxygen, and ultimately improves the sensitivity of the sensor.

3.2. Gas-sensing performance

During gas testing, the operation temperature is a very important factor. Changes in the operating temperature could influence the reaction kinetics of the gas molecules and oxygen adsorbed on the material's surface.⁴⁶ The relationship between the response and the operating temperature of the sintered sensor was investigated, and is shown in Fig. 8a. The results showed that the response of the sensor increases at first and then decreases with the change of working temperature in the temperature range from 130 to 400 °C. At a lower temperature, the oxygen adsorption rate is greater than the desorption rate. With the increase of temperature, the molecular weight of

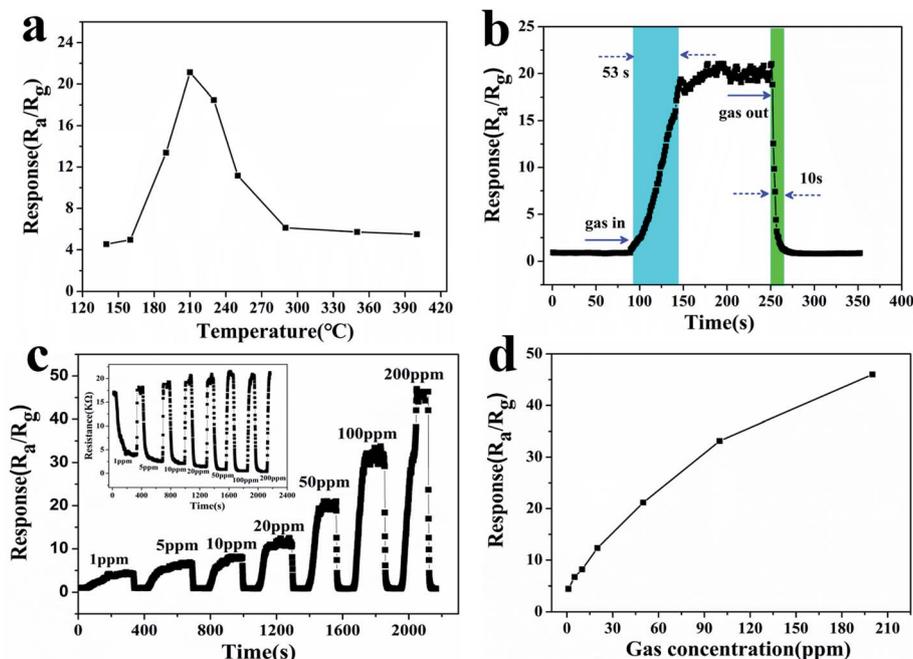


Fig. 8 (a) Sensitivity of the porous ZnSnO₃ nanocube sensor to 50 ppm formaldehyde under different test temperatures; (b) response–recovery curve of the porous ZnSnO₃ nanocube sensor to 50 ppm formaldehyde at 210 °C; (c) typical dynamic response–recovery curve of the porous ZnSnO₃ nanocube sensor to 1–200 ppm formaldehyde. The inset shows the curve of the sensor resistance to 1–200 ppm formaldehyde; (d) the response value curve of the porous ZnSnO₃ nanocube sensor to 1–200 ppm formaldehyde.



oxygen adsorbed on the surface of the gas-sensing material increases, and the sensitivity of the gas-sensing material increases. At a higher temperature, the oxygen adsorption rate is weaker than the desorption rate, and the adsorbed oxygen molecules are desorbed, so the sensitivity decreases with the increase of temperature.⁴⁷ The porous ZnSnO₃ nanocube sensor had a high response (21.2) to 50 ppm formaldehyde at 210 °C, and the adsorption–desorption rate reaches equilibrium. Thus, the operating temperature of 210 °C was selected as the optimum operating temperature for subsequent testing. Fig. 8b shows the response–recovery curve of the porous ZnSnO₃ nanocube sensor to 50 ppm formaldehyde at 210 °C. Under the test temperature of 210 °C, the response and recovery times of the porous ZnSnO₃ nanocube sensors to 50 ppm formaldehyde are 53 s and 10 s, respectively. Due to the porous structure having more active sites, more gas can diffuse into the material during the adsorption process and more oxygen is needed to deplete the electrons in the material during desorption, which eventually increases the response recovery time. The relationship between the response and the formaldehyde concentration for the porous ZnSnO₃ nanocube sensor can be observed in Fig. 8c and d. From the dynamic response curves in Fig. 8c, we can see that the response amplitude increases with the increase of formaldehyde concentration in the range of 1–200 ppm. The inset of Fig. 8c shows the curve of the sensor resistance to 1–200 ppm formaldehyde. With the increase of the gas concentration, the resistance of the material decreases. At lower concentrations (1–50 ppm), the sensor exhibits a linear

relationship between the sensor response and the formaldehyde concentration, while at higher concentrations (>50 ppm) the surface coverage tends to saturate and hence leads to a saturation of the response. Under the operating temperature of 210 °C, the sensor could detect 1 ppm formaldehyde with a sensitivity of 4.4 (Fig. 8d).

Gas-sensing repeatability is an important parameter to evaluate the gas-sensing ability of semiconductor materials. The porous ZnSnO₃ nanocube sensor was investigated with 50 ppm formaldehyde for 5 cycles at 210 °C (Fig. 9a). The response time and the recovery time, as well as the response values, are almost reproducible between 50 ppm formaldehyde and ambient air, which indicate that the sensor has good reversibility and repeatability for the detection of formaldehyde. Fig. 9c shows the gas sensing stability of the sensor. It can be seen that the responses of the sensor had an acceptable change after a pulse test for 90 days, indicating the good stability of the sensor. Gas selectivity is also an important index to evaluate the gas sensitivity. To detect the selectivity of the sensor, the sensitivities of the porous ZnSnO₃ nanocube sensor to different 50 ppm gases were tested at 210 °C. It can be seen from Fig. 9b that the response of the sensor to formaldehyde is significantly higher than that of other gases. The sensitivity (21.2) of the sensor to formaldehyde is twice as much as ethanol (11.2) and 3 times that of the other five gases, indicating that the prepared porous ZnSnO₃ nanocube sensor has good selectivity.

Table 1 shows the formaldehyde sensing performances of various ZnSnO₃ based gas sensors. Obviously, the response of

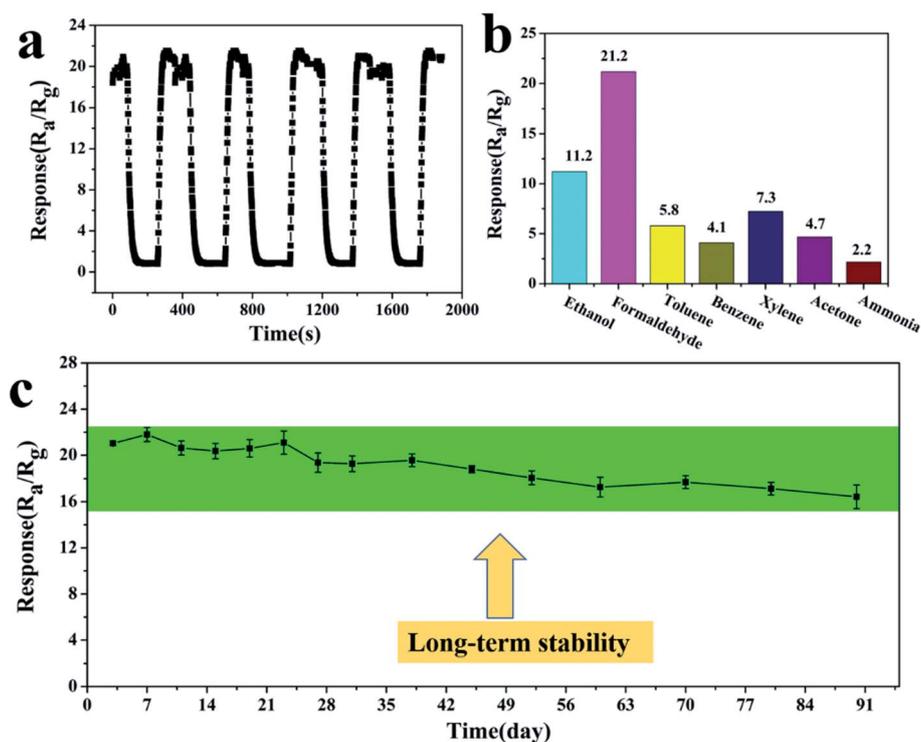


Fig. 9 (a) Repeatability of the porous ZnSnO₃ nanocube sensor to detect 50 ppm formaldehyde; (b) response values of the porous ZnSnO₃ nanocube sensor to different gases (all gas concentrations are 50 ppm); (c) long-term stability of the porous ZnSnO₃ nanocube sensor to detect 50 ppm formaldehyde.




Table 1 Comparison of the sensing performances of various ZnSnO₃-based gas sensors toward formaldehyde

| Materials | Operating tem. (°C) | Concentration (ppm) | Response (R_a/R_g) | Ref. |
|--|---------------------|---------------------|------------------------|--------------|
| ZnSnO ₃ hollow microspheres | 270 | 50 | ~5 | 48 |
| ZnSnO ₃ nanosheets | 300 | 20 | ~3 | 49 |
| ZnSnO ₃ /wt 10% SnO ₂ concave microcubes | 260 | 50 | ~5 | 50 |
| Porous ZnSnO ₃ cubes | 240 | 100 | 15 | 35 |
| ZnSnO ₃ hollow microspheres | 280 | 100 | ~5 | 51 |
| ZnSnO ₃ hollow nanocubes | 280 | 100 | ~6 | 52 |
| Hierarchical ZnSnO ₃ nanocages | 270 | 50 | 2 | 53 |
| Hollow ZnSnO ₃ cubic nanocages | 210 | 50 | 5.4 | 54 |
| Porous ZnSnO ₃ nanocubes | 210 | 50 | 21.2 | Present work |

the porous ZnSnO₃ nanocubes is much higher than those of mesoporous ZnSnO₃ hollow microspheres,⁴⁸ ZnSnO₃ nanosheets,⁴⁹ ZnSnO₃/wt 10% SnO₂ concave microcubes,⁵⁰ porous ZnSnO₃ cubes,³⁵ ZnSnO₃ hollow microspheres,⁵¹ ZnSnO₃ hollow nanocubes,⁵² hierarchical ZnSnO₃ nanocages⁵³ and hollow ZnSnO₃ cubic nanocages.⁵⁴ The gas sensing response enhancement may be attributed to the porous structure and the more numerous active centers obtained from the enhanced oxygen vacancy defects on the porous nanostructure, as shown in the PL spectra.

3.3. Gas-sensing mechanism

ZnSnO₃ is a typical surface-controlled gas-sensitive material. Fig. 10 shows the schematic diagrams of the gas sensing mechanism of the porous ZnSnO₃ nanocube sensor. In the air, oxygen atoms permeate through the surface of the material through physical adsorption and chemical adsorption, and capture electrons in the material to form negative O₂⁻, O²⁻, and O⁻ species,⁵⁵ resulting in an increase in the resistance of the ZnSnO₃ sensor, which can be described as follow:



Upon exposure to a reducing gas, the gas could react with the chemisorbed oxygen and then return the electron to the conduction band of the sensing material, decreasing the resistance of the sensor (Fig. 10a). This process leads to a shrinking electron transport barrier and a reduced electron depletion layer, resulting in a low resistance state (R_g) (Fig. 10b). The occurring reaction can be explained as followed:



When the gas is desorbed from the surface of the material, the electrons in the material will continue to react with oxygen to produce the corresponding adsorbed oxygen. In addition to the grain size effect, the excellent formaldehyde sensing properties of the porous ZnSnO₃ nanocubes can be attributed to the porous structure and large specific surface area (70.001 m² g⁻¹), which means that more formaldehyde and oxygen molecules can be adsorbed on the ZnSnO₃ surface.

4. Conclusions

In summary, porous ZnSnO₃ nanocubes are successfully synthesized by a facile hydrothermal method combined with subsequent calcination. The size of the ZnSnO₃ nanocubes is about 100 nm and the corresponding specific surface area is 70.001 m² g⁻¹. The porous structure could increase the concentration of the oxygen vacancies, thereby increasing the number of active sites, which is verified by the TEM and PL results. The gas sensing performance showed that the porous ZnSnO₃ nanocubes sensor could detect 50 ppm formaldehyde at about 210 °C with a response value of 21.2, which is 3 times that of the other gases. The sensor has a higher sensitivity which

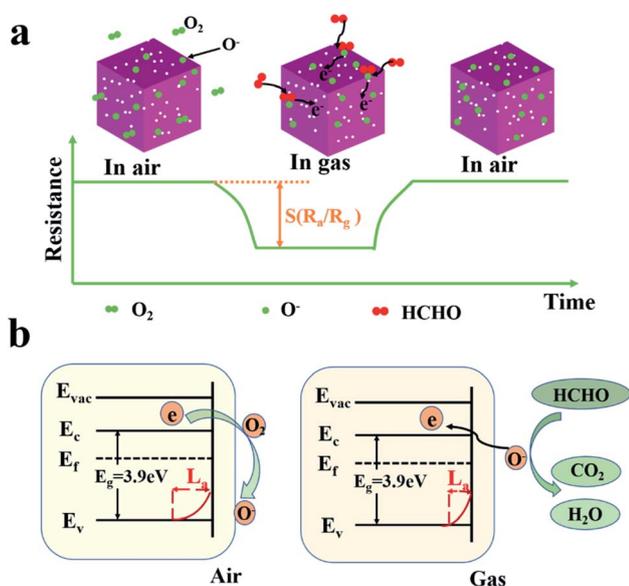


Fig. 10 Schematic diagrams of the gas sensing mechanism of the porous ZnSnO₃ nanocube sensors. (a) Schematic diagram of the resistance change; (b) schematic diagram of the energy band theory.



may possibly result from the porous structure and more numerous exposed active sites. After 90 days of testing, the sensor still has high sensitivity to formaldehyde. Therefore, the prepared porous ZnSnO₃ nanocubes can be regarded as one of the promising sensing materials for the efficient detection of formaldehyde.

Author contributions

Jiaoling Zheng: experimental operation, writing – review & editing. Huanhuan Hou: experimental operation. Hao Fu: data curation, formal analysis. Liping Gao: conception, supervision, data curation. Hongjie Liu: data curation, formal analysis.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge the Science and Technology Plan Project of Chuzhou (2019ZN005) and the College Students Innovation and Entrepreneurship Training Project (202010377023).

References

- M. Mori, Y. Itagaki and Y. Sadaoka, Effect of VOC on ozone detection using semiconducting sensor with SmFe_{1-x}Co_xO₃ perovskite-type oxides, *Sens. Actuators, B*, 2012, **163**, 44–50.
- Y. Zeng, T. Zhang, L. Wang, M. Kang, H. Fan, R. Wang and Y. He, Enhanced toluene sensing characteristics of TiO₂-doped flowerlike ZnO nanostructures, *Sens. Actuators, B*, 2009, **140**, 73–78.
- A. Allouch, M. Guglielmino, P. Bernhardt, C. A. Serra and S. L. Calvé, Transportable, fast and high sensitive near real-time analyzers: formaldehyde detection, *Sens. Actuators, B*, 2013, **181**, 551–558.
- T. S. Wang, B. Jiang, Q. Yu, X. Y. Kou, P. Sun, F. M. Liu, H. Y. Lu, X. Yan and G. Y. Lu, Realizing the Control of Electronic Energy Level Structure and Gas-Sensing Selectivity over Heteroatom Doped In₂O₃ Spheres with an Inverse Opal Microstructure, *ACS Appl. Mater. Interfaces*, 2019, **11**, 9600–9611.
- J. A. Dirksen, K. Duval and T. A. Ring, NiO thin-film formaldehyde gas sensor, *Sens. Actuators, B*, 2001, **80**, 106–115.
- L. P. Liu, X. G. Li, P. K. Dutta and J. Wan, Room temperature impedance spectroscopy-based sensing of formaldehyde with porous TiO₂ under UV illumination, *Sens. Actuators, B*, 2013, **185**, 1–9.
- G. R. Mohimann, Formaldehyde detection in air by laser induced fluorescence, *Appl. Spectrosc.*, 1985, **39**, 98–101.
- E. Norkus, A. Vaskelis and R. Pauliukaite, Polarographic Determination of Formaldehyde According to the Anodic Oxidation Wave in Alkaline Solutions, *Electroanalysis*, 1999, **11**, 447–449.
- X. L. Wang and L. Zhang, Headspace-Gas Chromatography Method for Determination of Formaldehyde Content in Wastewater, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2021, **647**, 012155.
- Z. J. Wang, J. Liu, F. J. Wang, S. Y. Chen, H. Luo and X. B. Yu, Size-Controlled Synthesis of ZnSnO₃ Cubic Crystallites at Low Temperatures and Their HCHO-Sensing Properties, *J. Phys. Chem. C*, 2010, **114**, 13577–13582.
- L. Q. Shi, J. B. Cui, F. Zhao, D. J. Wang, T. F. Xie and Y. H. Lin, High-performance formaldehyde gas-sensors based on three-dimensional center-hollow ZnO, *Phys. Chem. Chem. Phys.*, 2015, **173**, 1316–13123.
- Y. X. Li, N. Chen, D. Y. Deng, X. X. Xing, X. C. Xiao and Y. D. Wang, Formaldehyde detection: SnO₂ microspheres for formaldehyde gas sensor with high sensitivity, fast response/recovery and good selectivity, *Sens. Actuators, B*, 2017, **238**, 264–273.
- Z. H. Tao, Y. W. Li, B. Zhang, G. Sun, M. Xiao, H. Bala, J. L. Cao, Z. Y. Zhang and Y. Wang, Synthesis of urchin-like In₂O₃ hollow spheres for selective and quantitative detection of formaldehyde, *Sens. Actuators, B*, 2019, **298**, 126889.
- B. Bouchikhi, T. Chludziński, T. Saidi, J. Smulko, N. E. Bari, H. Wen and R. Ionescu, Formaldehyde detection with chemical gas sensors based on WO₃ nanowires decorated with metal nanoparticles under dark conditions and UV light irradiation, *Sens. Actuators, B*, 2020, **320**, 128331.
- C. L. Zhao, Y. F. Ren, S. S. Chen, L. Yang and Y. Guo, The enhanced ethanol sensing properties obtained by the introduction of NiO into ZnO/SnO₂ mixed metal oxides, *J. Solid State Chem.*, 2018, **265**, 345–352.
- C. H. Liu, R. Röder, L. C. Zhang, Z. Ren, H. Y. Chen, Z. H. Zhang, C. Ronning and P. X. Gao, Highly efficient visible-light driven photocatalysts: a case of zinc stannate based nanocrystalassemblies, *J. Mater. Chem. A*, 2014, **2**, 4157–4167.
- L. Y. Du, D. X. Wang, K. K. Gu and M. Z. Zhang, Construction of PdO-decorated double-shell ZnSnO₃ hollow microspheres for n-propanol detection at low temperature, *Inorg. Chem. Front.*, 2021, **8**, 787–795.
- H. Men, P. Gao, B. B. Zhou, Y. J. Chen, C. L. Zhu, G. Xiao, L. Q. Wang and M. L. Zhang, Fast synthesis of ultra-thin ZnSnO₃ nanorods with high ethanol sensing properties, *Chem. Commun.*, 2010, **46**, 7581–7583.
- B. S. Wang, J. B. Yu, X. H. Li, J. Yin and M. Chen, Synthesis and high formaldehyde sensing properties of quasi two-dimensional mesoporous ZnSnO₃ nanomaterials, *RSC Adv.*, 2019, **9**, 14809–14816.
- X. Y. Wang, H. Li, X. T. Zhu, M. Z. Xia, T. Tao, B. X. Leng and W. Xu, Improving ethanol sensitivity of ZnSnO₃ sensor at low temperature with multi-measures: Mg doping, nano-TiO₂ decoration and UV radiation, *Sens. Actuators, B*, 2019, **297**, 126745.
- Y. L. Qin, F. F. Zhang, X. C. Du, G. Huang, Y. C. Liu and L. M. Wang, Controllable synthesis of cube-like ZnSnO₃@TiO₂ nanostructures as lithium-ion battery anodes, *J. Mater. Chem. A*, 2015, **3**, 2985–2990.



- 22 Z. Y. Wang, J. Y. Miao, H. X. Zhang, D. Wang and J. B. Sun, Hollow cubic ZnSnO₃ with abundant oxygen vacancies for H₂S gas sensing, *J. Hazard. Mater.*, 2020, **391**, 122226.
- 23 F. Guo, X. L. Huang, Z. H. Chen, H. J. Ren, M. Y. Li and L. Z. Chen, MoS₂ nanosheets anchored on porous ZnSnO₃ cubes as an efficient visible-light-driven composite photocatalyst for the degradation of tetracycline and mechanism insight, *J. Hazard. Mater.*, 2020, **390**, 122158.
- 24 Y. Y. Yin, Y. B. Shen, P. F. Zhou, R. Lu, A. Li, S. K. Zhao, W. G. Liu, D. Z. Wei and K. F. Wei, Fabrication, characterization and n-propanol sensing properties of perovskite-type ZnSnO₃ nanospheres based gas sensor, *Appl. Surf. Sci.*, 2020, **509**, 145335.
- 25 G. Q. Feng, Y. H. Che, C. W. Song, J. K. Xiao, X. F. Fan, S. Sun, G. H. Huang and Y. C. Ma, Morphology-controlled synthesis of ZnSnO₃ hollow spheres and their n-butanol gas-sensing performance, *Ceram. Int.*, 2021, **47**, 2471–2482.
- 26 H. Men, P. Gao, B. B. Zhou, Y. J. Chen, C. L. Zhu, G. Xiao, L. Q. Wang and M. L. Zhang, Fast synthesis of ultra-thin ZnSnO₃ nanorods with high ethanol sensing properties, *Chem. Commun.*, 2010, **46**, 7581–7583.
- 27 G. Wang, Y. Xi, H. Xuan, R. Liu, X. Chen and L. Cheng, Hybrid nanogenerators based on triboelectrification of a dielectric composite made of lead-free ZnSnO₃ nanocubes, *Nano Energy*, 2015, **18**, 28–36.
- 28 Y. Yin, F. Li, N. Zhang, S. Ruan, H. Zhang and Y. Chen, Improved gas sensing properties of silver functionalized ZnSnO₃ hollow nanocubes, *Inorg. Chem. Front.*, 2018, **5**, 2123–2131.
- 29 L. L. Wang, T. Fei, Z. Lou and T. Zhang, Three-dimensional hierarchical flowerlike-Fe₂O₃ nanostructures: synthesis and ethanol-sensing properties, *ACS Appl. Mater. Interfaces*, 2011, **3**, 4689–4694.
- 30 Y. H. Li, W. Luo, N. Qin, J. P. Dong, J. Wei, W. Li, S. S. Feng, J. C. Chen, J. Q. Xu, A. A. Elzatahry, M. H. Es-Saheb, Y. H. Deng and D. Y. Zhao, Highly ordered mesoporous tungsten oxides with a large pore size and crystalline framework for H₂S sensing, *Angew. Chem., Int. Ed.*, 2014, **53**, 9035–9040.
- 31 Q. J. Fu, M. M. Ai, Y. Duan, L. M. Lu, X. Tian, D. D. Sun, Y. Y. Xu and Y. Q. Sun, Synthesis of uniform porous NiO nanotetrahedra and their excellent gas-sensing performance toward formaldehyde, *RSC Adv.*, 2017, **7**, 52312–52320.
- 32 K. Yang, J. Z. Ma, X. K. Qiao, Y. W. Cui, L. C. Jia and H. Q. Wang, Hierarchical porous LaFeO₃ nanostructure for efficient trace detection of formaldehyde, *Sens. Actuators, B*, 2020, **313**, 128022.
- 33 D. Sun, H. X. Guo, Y. Li, H. Y. Li, X. S. Li, C. X. Tian, J. X. Zhang and L. Liu, 3D ordered porous SnO₂ with a controllable pore diameter for enhanced formaldehyde sensing performance, *Funct. Mater. Lett.*, 2020, **13**, 2051044.
- 34 L. P. Gao, Z. X. Cheng, Q. Xiang, Y. Zhang and J. Q. Xu, Porous Corundum-type In₂O₃ nanosheets: Synthesis and NO₂ sensing properties, *Sens. Actuators, B*, 2015, **208**, 436–443.
- 35 J. R. Huang, X. J. Xu, C. P. Gu, W. Z. Wang, B. Y. Geng, Y. F. Sun and J. H. Liu, Size-controlled synthesis of porous ZnSnO₃ cubes and their gas-sensing and photocatalysis properties, *Sens. Actuators, B*, 2012, **171–172**, 572–579.
- 36 Y. K. Wang and J. M. Zhang, Synthesis and Electrochemical Performance of Amorphous ZnSnO₃ Hollow Cubes, *J. Chin. Ceram. Soc.*, 2016, **44**, 1434–1440.
- 37 F. Han, W. C. Li, C. Lei, B. He, K. Oshida and A. H. Lu, Selective Formation of Carbon-Coated, Metastable Amorphous ZnSnO₃ Nanocubes Containing Mesopores for Use as High-Capacity Lithium-Ion Battery, *Small*, 2014, **10**, 2637–2644.
- 38 X. F. Li, X. B. Meng, J. Liu, D. S. Geng, Y. Zhang, M. N. Banis, Y. L. Li, J. L. Yang, R. Y. Li, X. L. Sun, M. Cai and M. W. Verbrugge, Tin Oxide with Controlled Morphology and Crystallinity by Atomic Layer Deposition onto Graphene Nanosheets for Enhanced Lithium Storage, *Adv. Funct. Mater.*, 2012, **22**, 1647–1654.
- 39 Z. Y. Wang, Z. C. Wang, W. T. Liu, W. Xiao and X. W. Lou, Amorphous CoSnO₃@C nanoboxes with superior lithium storage capability, *Energy Environ. Sci.*, 2013, **6**, 87–91.
- 40 S. Y. Dong, J. Y. Sun, Y. K. Li, C. F. Yu, Y. H. Li and J. H. Sun, ZnSnO₃ hollow nanospheres/reduced graphene oxide nanocomposites as high-performance photocatalysts for degradation of metronidazole, *Appl. Catal., B*, 2014, **144**, 386–393.
- 41 F. Gu, S. F. Wang, M. K. Lü, X. F. Cheng, S. W. Liu, G. J. Zhou, D. Xu and D. R. Yuan, Luminescence of SnO₂ thin films prepared by spin-coating method, *J. Cryst. Growth*, 2004, **262**, 182–185.
- 42 H. Sefardjella, B. Boudjema, A. Kabir and G. Schmerber, Structural and photoluminescence properties of SnO₂ obtained by thermal oxidation of evaporated Sn thin films, *Curr. Appl. Phys.*, 2013, **13**, 1971–1974.
- 43 I. Saafi, R. Dridi, R. Mimouni, A. Amlouk, A. Yumak, K. Boubaker, P. Petkova and M. Amlouk, Microstructural and optical properties of SnO₂-ZnSnO₃ ceramics, *Ceram. Int.*, 2016, **42**, 6273–6281.
- 44 A. B. Djurišić, W. C. H. Choy, V. A. L. Roy, Y. H. Leung, C. Y. Kwong, K. W. Cheah, T. K. GunduRao, W. K. Chan, H. Fei Lui and C. Surya, Photoluminescence and Electron Paramagnetic Resonance of ZnO Tetrapod Structures, *Adv. Funct. Mater.*, 2004, **14**, 856–864.
- 45 Q. Zhang, S. P. Wang, L. W. Wang, Y. L. Huang, Y. H. Wang, K. F. Yu and L. P. Gao, Vapor-phase Modulated Sphere-like In₂O₃@N-C Complexes for Improving Gas Sensitivity, *J. Alloys Compd.*, 2021, **865**, 158702.
- 46 H. Li, W. Y. Xie, B. Liu, Y. R. Wang, S. H. Xiao, X. C. Duan, Q. H. Li and T. H. Wang, Ultra-fast and highly-sensitive gas sensing arising from thin SnO₂ inner wall supported hierarchical bilayer oxide hollow spheres, *Sens. Actuators, B*, 2017, **240**, 349–357.
- 47 L. P. Gao, H. Fu, J. J. Zhu, J. H. Wang, Y. P. Chen and H. J. Liu, Synthesis of SnO₂ nanoparticles for formaldehyde detection with high sensitivity and good selectivity, *J. Mater. Res.*, 2020, **35**, 2208–2217.



- 48 Y. F. Bing, Y. Zeng, C. Liu, L. Qiao, Y. M. Sui a, B. Zou, W. T. Zheng and G. T. Zou, Assembly of hierarchical ZnSnO₃ hollow microspheres from ultra-thin nanorods and the enhanced ethanol-sensing performances, *Sens. Actuators, B*, 2014, **190**, 370–377.
- 49 L. Y. Du, H. P. Zhang, M. M. Zhu and M. Z. Zhang, Construction of flower-like ZnSnO₃/Zn₂SnO₄ hybrids for enhanced phenylamine sensing performance, *Inorg. Chem. Front.*, 2019, **6**, 2311–2317.
- 50 J. T. Zhang, X. H. Jia, D. D. Lian, J. Yang, S. Z. Wang, Y. Li and H. J. Song, Enhanced selective acetone gas sensing performance by fabricating ZnSnO₃/SnO₂ concave microcube, *Appl. Surf. Sci.*, 2021, **542**, 148555.
- 51 X. H. Jia, M. G. Tian, R. R. Dai, D. D. Lian, S. Han, X. Y. Wu and H. J. Song, One-pot template-free synthesis and highly ethanol sensing properties of ZnSnO₃ hollow microspheres, *Sens. Actuators, B*, 2017, **240**, 376–385.
- 52 Y. Y. Yin, F. Li, N. Zhang, S. P. Ruan, H. F. Zhang and Y. Chen, Improved gas sensing properties of silver-functionalized ZnSnO₃ hollow nanocubes, *Inorg. Chem. Front.*, 2018, **5**, 2123–2131.
- 53 Y. Zeng, K. Zhang, X. L. Wang, Y. M. Sui, B. Zou, W. T. Zheng and G. T. Zou, Rapid and selective H₂S detection of hierarchical ZnSnO₃ nanocages, *Sens. Actuators, B*, 2011, **159**, 245–250.
- 54 Y. Zeng, X. L. Wang and W. T. Zheng, Synthesis of Novel Hollow ZnSnO₃ Cubic Nanocages and Their HCHO Sensing Properties, *J. Nanosci. Nanotechnol.*, 2013, **13**, 1286–1290.
- 55 X. An, J. C. Yu, Y. Wang, Y. Hu, X. Yu and G. Zhang, WO₃ nanorods/graphene nanocomposites for high-efficiency visible-light-driven photocatalysis and NO₂ gas sensing, *J. Mater. Chem.*, 2012, **22**, 8525–8531.

