

Cite this: *J. Mater. Chem. C*, 2021,  
9, 17158

## Optical and magnetic characterization of one-dimensional Cu(II)-based perovskite: a high UV–Vis–NIR absorber†

Wiem Jabeur,<sup>a</sup> Rawia Msalmi,<sup>a</sup> Marcus Korb,<sup>b</sup> Mariia Holub,<sup>ib</sup> c Edoardo Mosconi,<sup>d</sup> Erik Čižmár,<sup>ib</sup> c Anowar Tozri,<sup>e</sup> Numa A. Althubiti\*<sup>e</sup> and Houcine Naili <sup>ib</sup> \*<sup>a</sup>

A one dimensional copper(II)-based perovskite,  $(C_5H_8N_3)[CuCl_3]$ , was successfully synthesized. XR-diffraction demonstrates that the mineral framework of this perovskite is formed by infinite needle-like chains  $[CuCl_3]_{\infty}^-$ , where each  $Cu^{2+}$  ion, with its [4+2] coordination sphere, adopts a nearly tetragonal symmetry. The simultaneous TGA/DSC analyses demonstrate the stability of the material at ambient temperature and up to 130 °C. The convergence of the optical experimental results and the theoretical DFT calculations of the electronic structure demonstrates the semiconducting character of the synthesized compound with an experimental direct band gap energy of 2.21 eV. The optical analysis shows that a cooperative Jahn–Teller effect is manifested around the copper ions. Both ligand to metal charge transfer (LMCT) transitions and crystal field transitions (d–d) make the material suitable for green solar cell applications. The magnetic properties of  $(C_5H_8N_3)[CuCl_3]$  can be described by a model of  $S = 1/2$  antiferromagnetic dimers with exchange interaction  $J/k_B = -122.7$  K.

Received 10th September 2021,  
Accepted 7th November 2021

DOI: 10.1039/d1tc04336f

rsc.li/materials-c

## Introduction

Since 2009, three dimensional (3D) lead halide perovskites that are derived from the parent structure  $ABX_3$  (with  $A = CH_3NH_3$  or  $HC(NH_2)_2$ ;  $B = Pb$  and  $X = Br, Cl, \text{ or } I$ ) have attracted significant attention in the photovoltaic (PV) solar cell (SC) community<sup>1,2</sup> In particular,  $CH_3NH_3PbI_3$  and  $CH_3NH_3PbBr_3$  result in high performance in SCs due to their simplicity of deposition and semiconducting properties with high electron–photon conversion efficiency (EPCE) reaching 3.8% for  $CH_3NH_3PbI_3$ .<sup>1</sup> Unfortunately, the application of Pb-based perovskites in SCs suffers from the limitation of their commercialization because of the use of the environmentally, as well as health, hazardous lead.<sup>3</sup> In addition, lead halide perovskites are thermally unstable and have shown high degradation under real-world conditions; they

must be protected from oxygen and moisture.<sup>4,5</sup> Nowadays, the increasing exigency in the environmentally friendly energy conversion devices has led to the advancement of lead-free perovskite SCs. Theoretical studies on the electronic properties of Pb-based perovskites have shown that their electronic structure and the existence of the dormant 6s orbitals are accountable for the PV performance. So, an effective strategy to achieve non-hazardous SC devices is the substitution of the Pb ions by other cations that comprise the dormant s orbitals, such as  $Ge^{2+}$ ,  $Sn^{2+}$ ,  $Bi^{3+}$ , and  $Cu^{2+}$ .<sup>6–9</sup> Despite their promising EPCE of 13%,<sup>8</sup> comparable to Pb-based SCs, the Sn-based devices exhibit instability because of their oxidation and ambient hydrolysis.<sup>10</sup> Due to their smaller atomic radius than that of Pb, the application of transition metals to substitute Pb led towards the stabilization of two-dimensional hybrid perovskites  $(RNH_3)_2MX_4$ .<sup>11,12</sup> This reduction of the dimensionality from 3D to 2D generates major changes in the optical, magnetic and dielectric properties due to the multi-quantum electronic structure of 2D perovskites.<sup>13</sup> A typical two dimensional perovskite exhibits a value of excitonic binding energy up to 300 meV and its large band gaps make it suitable for light emitting devices.<sup>14</sup> In the last years, Cu-based low dimensional perovskites have been extensively studied due to their high piezoelectric as well as ferro/antiferromagnetic responses.<sup>15–17</sup> Recently, Cu-based 2D perovskites have demonstrated their performance as alternative to Pb-based absorbers in SCs. In 2016, D. Cortecchia *et al.* studied the optoelectronic properties of a series of

<sup>a</sup> Laboratory Physico Chemistry of the Solid State, Department of Chemistry, Faculty of Sciences of Sfax, Sfax University, Tunisia. E-mail: houcine\_naili@yahoo.com

<sup>b</sup> The University of Western Australia, Faculty of Sciences, School of Molecular Sciences, 35 Stirling Highway, Crawley, Perth, Western Australia 6009, Australia

<sup>c</sup> P.J. Šafárik University in Košice, Faculty of Sciences, Institute of Physics, Park Angelinum 9, SK-041 54 Košice, Slovakia

<sup>d</sup> Computational Laboratory for Hybrid/Organic Photovoltaics (CLHYO), Istituto CNR di Scienze e Tecnologie Chimiche “Giulio Natta” (CNR-SCITEC), Via Elce di Sotto 8, 06123 Perugia, Italy

<sup>e</sup> Physics Department, College of Science, Jouf University, Sakaka 2014, Saudi Arabia. E-mail: naalthubiti@ju.edu.sa

† Electronic supplementary information (ESI) available. CCDC 1897590. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1tc04336f

$\text{MA}_2\text{CuCl}_x\text{Br}_{4-x}$  layered perovskites, which are characterized with gap energies ranging 2.8 and 3.1 eV, and proved their performance for green SC applications with a low power conversion efficiency (PCE) reaching only 0.017% with  $\text{MA}_2\text{CuCl}_4$ .<sup>9</sup> This very low efficiency was related to the low absorption coefficient in the visible region, and authors revealed that the integration of aromatic organic cations with transition metals in the low dimensional perovskites will improve their PV performance compared to  $\text{MA}_2\text{CuCl}_x\text{Br}_{4-x}$ . This prediction is proved by the reported  $\text{C}_6\text{H}_4\text{NH}_2\text{CuBr}_2\text{I}$  which exhibits a PCE of 0.5%.<sup>18</sup> In a report by Cui *et al.* a PV device based on (*p*- $\text{F-C}_6\text{H}_5\text{C}_2\text{H}_4\text{NH}_3$ )<sub>2</sub> $\text{CuBr}_4$  perovskite, with band gap energy of 1.74 eV, revealed a PCE of 0.51%.<sup>19</sup> Moreover, low-dimensional Cu-based metal halides have recently attracted great attention due to their excellent good stability under ambient conditions.<sup>20–22</sup> The two-dimensional layered ( $\text{C}_6\text{H}_5\text{CH}_2\text{NH}_3$ )<sub>2</sub> $\text{CuBr}_4$  perovskite, investigated for SC application with a PCE of 2.0%, is humidity-stable, heat-stable, and ultraviolet (UV) light-stable.<sup>23</sup> Recently, K. Ahmad and S. M. Mobin have employed high water-stable (Cu)-based perovskites ( $\text{C}_6\text{H}_4\text{NH}_2\text{CuBr}_2\text{I}$  and  $\text{C}_6\text{H}_4\text{NH}_2\text{CuCl}_2\text{I}$ ) as light absorbers for the development of Pb-free PSCs.<sup>24</sup> Most two dimensional Cu-based perovskites showed a green emission band around 500 nm. A. Elseman *et al.* developed ( $\text{CH}_3\text{NH}_3$ )<sub>2</sub> $\text{CuX}_4$ -based perovskite SCs and indicated that ( $\text{CH}_3\text{NH}_3$ )<sub>2</sub> $\text{CuCl}_4$  presents photoluminescent properties.<sup>25</sup> Then, R. Valiente and F. Rodriguez have commented this work and demonstrated that this material does not show any photoluminescence under UV-excitation and that this is extended to all others copper(II) based 2D perovskites previously studied.<sup>26</sup> In fact, the d–d transitions improve visible light absorption and enhance PCE.<sup>9,26</sup> Hence, the use of Cu(II) blocks the photoluminescence mechanism, thanks to the d–d electronic transitions within the  $\text{Cu}^{2+}$  cation. Recently, a 1D Cu-based perovskite ( $\text{C}_5\text{H}_{14}\text{N}_2$ ) $[\text{CuCl}_4]$ , characterized with an energy gap of 2.56 eV, has been developed by our group as a light absorber material for SC applications.<sup>27</sup> In the present work, a novel low dimensional lead free perovskite, ( $\text{C}_5\text{H}_8\text{N}_3$ ) $[\text{CuCl}_3]$ , is synthesized for green SC applications.

## Experimental section

### Materials

Given the importance of obtaining high quality crystals, all the employed chemicals and reagents were received from commercial sources (Sigma-Aldrich).  $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$  (99.999%) and  $\text{C}_5\text{H}_7\text{N}_3$  (97%) were used without further purification. Hydrochloric acid (HCl) and distilled water were introduced into this synthesis.

### Synthesis

( $\text{C}_5\text{H}_8\text{N}_3$ ) $[\text{CuCl}_3]$  was prepared via slow evaporation technique at room temperature. 0.2 mg of 2-Amino-4-methylpyrimidine was dissolved in 5 ml of distilled water; hydrochloric acid (HCl) (pH  $\approx$  2.5) was added drop by drop to the solution and stirred

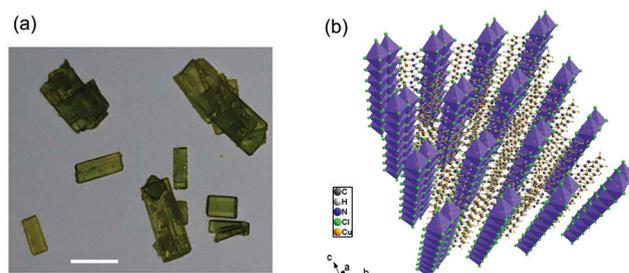


Fig. 1 (a) Microscopy image of the microcrystals (scale bar, 25  $\mu\text{m}$ ) and (b) perspective view of the structure of ( $\text{C}_5\text{H}_8\text{N}_3$ ) $[\text{CuCl}_3]$ .

with 5 ml of solution containing 0.17 mg of  $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$  until the solution became clear. The mixture was stirred for 30 minutes using a magnetic stirrer and slowly evaporated at room temperature. Green single crystals, with suitable dimensions for crystallographic study, were collected after a few days. The microscope image in Fig. 1(a) shows the morphology of the crystals.

### Instruments

The FT-IR spectrum was obtained using a PerkinElmer 1600FT spectrometer with frequency in the range of 500 and 4000  $\text{cm}^{-1}$  by producing on a pressed pellet of the powdered sample dispersed in KBr at room temperature. The UV–Vis–NIR diffuse reflectance spectrum was recorded at room temperature using a Varian Carry 5000 spectrophotometer. TGA–DSC measurements (10.416 mg sample) were performed using a Mettler Toledo TGA/DSC1 1100 system with a UMX1 balance, in a hermetically sealed capsule under thermal recording conditions at a heating rate of 10  $\text{K min}^{-1}$  between 40  $^\circ\text{C}$  and 800  $^\circ\text{C}$ , and an argon flow of 20  $\text{ml min}^{-1}$ . The magnetic properties were measured using a Quantum Design MPM3 magnetometer on a nascent polycrystalline sample held in a gelatin capsule. The diamagnetic contribution of the capsule, core diamagnetism estimated using Pascal's constants, and typical temperature-independent paramagnetism were subtracted from the measured data.

### X-ray diffraction analysis

Data of ( $\text{C}_5\text{H}_8\text{N}_3$ ) $[\text{CuCl}_3]$  were collected using an Oxford Gemini S diffractometer with  $\text{Mo K}_\alpha$  radiation ( $\lambda = 0.71073 \text{ \AA}$ ) at 125 K. The molecular structure was solved by direct methods using SHELXS-13<sup>28</sup> and refined by full-matrix least-squares procedures on  $F^2$  using SHELXL-13.<sup>29</sup> A summary of the important crystallographic data, data collection and refinement details is presented in Table S1 (ESI<sup>†</sup>). Two main domains were present in the used crystal and hence, two-component twin integration was carried out resulting in a BASF of 0.5967. All non-hydrogen atoms were refined anisotropically. Hydrogen atoms were placed in calculated positions and constrained to ride on their parent atoms with  $U_{\text{iso}}(\text{H}) = 1.2 U_{\text{eq}}(\text{C})$  and a X–H distance of 0.93  $\text{Å}$  for aromatic (X = C, N),  $U_{\text{iso}}(\text{H}) = 1.5 U_{\text{eq}}(\text{C})$  and a C–H distance of 0.96  $\text{Å}$  for methyl, and  $U_{\text{iso}}(\text{H}) = 1.2 U_{\text{eq}}(\text{C})$  and a N–H distance of 0.86  $\text{Å}$  for the  $\text{NH}_2$ –H atoms. The latter was

treated as a terminal CH<sub>2</sub> group in order to reduce the number of parameters in the non-centrosymmetric space group.

### Computational details

**Electronic structure investigation.** All calculations have been performed using the Quantum Espresso program package.<sup>30</sup> Geometry optimization was carried out by keeping the experimental cell parameters fixed and relaxing only the atomic positions using the PBE exchange correlation functional<sup>31</sup> and a  $2 \times 2 \times 2$  *k*-point mesh grid. The core–valence electron interactions were described using ultrasoft pseudo potentials (shells explicitly included in calculations: Cl 3s3p; N, C 2s2p; H 1s; Cu 3s3p3d4s) and a cutoff on the wavefunctions of 25 Ryd (200 Ryd on the charge density). For simulating the electronic structure, a single point calculation on the relaxed geometries has been carried out using the HSE06 functional,<sup>32</sup> a  $2 \times 1 \times 1$  *k*-point mesh grid and a cutoff on the wavefunctions of 70 Ryd (280 Ryd on the charge density). For the hybrid HSE06 calculation, we adopted scalar-relativistic norm-conserving pseudo potentials with electrons from H 1s; C 2s2p; N 2s2p; Cl 3s3p; and Cu 3s3p3d4s shells explicitly included in the calculations.

**Magnetic simulation.** The Broken Symmetry (BS) DFT calculations<sup>33</sup> were performed using the ORCA 5.0.0 computational package<sup>34</sup> using the B3LYP exchange–correlation functional.<sup>35</sup> The exchange interaction was obtained using the Yamaguchi formalism<sup>36</sup>  $J_{BS} = -\frac{E_{HS} - E_{BS}}{\langle S^2 \rangle_{HS} - \langle S^2 \rangle_{BS}}$  from single-point approach (using the X-ray determined structure), with a spin Hamiltonian in the form  $\hat{H} = -2J_{BS}\hat{S}_1\hat{S}_2$ . Relativistic effects were taken into account by using the zeroth-order regular approximation (ZORA)<sup>37,38</sup> together with the corresponding segmented all-electron relativistic contracted (SARC) version of the triple- $\zeta$  basis set Def2-TZVP<sup>39,40</sup> for all atoms. All calculations utilized the RI approximation, and the chain-of-spheres (RIJCOSX) approximation to exact exchange<sup>41</sup> with appropriate decontracted auxiliary basis sets SARC/J and Def2-TZVP/C.<sup>42,43</sup> Integration grid DefGrid2 and tight SCF convergence criteria were used.

## Results

### Description of the crystal structure

(C<sub>5</sub>H<sub>8</sub>N<sub>3</sub>)[CuCl<sub>3</sub>] crystallizes in the centrosymmetric space group *P* $\bar{1}$  of the triclinic system with *Z* = 2. All the measurement conditions and crystallographic parameters are collated in Table S1 (ESI<sup>†</sup>). The asymmetric unit consists of one CuCl<sub>3</sub> inorganic fragment and one organic cation [C<sub>5</sub>H<sub>8</sub>N<sub>3</sub>]<sup>+</sup>. The molecular crystal visualization, in Fig. 1(b), shows that the structure is formed with infinite polymeric inorganic fragments extended along the [100] direction. These inorganic chains are separated by the organic protonated molecules. As described in Fig. 2(a), the inorganic part of this structure is formed with parallel slipped stacks of an edge-shared bis(square planar) cluster [Cu<sub>2</sub>Cl<sub>6</sub>]. Therein, the copper ions interact with the Cl1 atom of the above and the Cl3 atom of the below-positioned

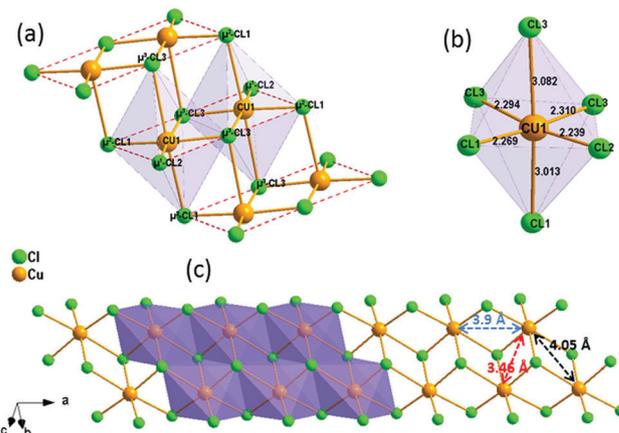


Fig. 2 Detailed presentation of the inorganic polymeric fragment: (a) description of the Cl and Cu ion environments, (b) geometric description of the CuCl<sub>6</sub> octahedron, and (c) view of a single [CuCl<sub>3</sub>]<sub>∞</sub> inorganic chain.

layers. Hence, the copper(II) coordination is transformed from the square planar to the [4+2] coordination sphere where the Cu<sup>2+</sup> ions adopt a nearly tetragonal symmetry. The Cu<sup>2+</sup> anion is surrounded by one terminal chlorine μ<sup>1</sup>-Cl<sub>2</sub>, two doubly bridging μ<sup>2</sup>-Cl<sub>1</sub> and three triply bridging μ<sup>3</sup>-Cl<sub>3</sub> (see Fig. 2(a and b)). The four equatorial Cu–Cl bonds have the values 2.269(2), 2.239(2), 2.294(2) and 2.310(2) Å while the two axial distances are 3.013 and 3.082 Å. The distortion index (*A*) of the [CuCl<sub>6</sub>]<sup>2-</sup> octahedron was calculated using eqn (1) and found to be  $2.06 \times 10^{-2}$ , being too close to that of (C<sub>5</sub>H<sub>14</sub>N<sub>2</sub>)[CuCl<sub>4</sub>], which indicates that the hexa-chlorocuperate(II) octahedra are highly distorted and that the Jahn Teller effect is arising around the copper ions.

$$A = \frac{1}{6} \sum_{i=1}^6 \frac{(d_i - \bar{d})^2}{\bar{d}^2} \quad (1)$$

where  $\bar{d}$  is the average value of the Cu–Cl distances and  $d_i$  are the six Cu–Cl distances.

The view of the inorganic part in Fig. 2(c) shows that the mineral polymeric fragment is formed by two infinite strings along the *a*-axis. Each string is formed with two opposed edges shared CuCl<sub>6</sub> octahedra. These strings are condensed together through three μ<sup>3</sup>-Cl ions in a way that each octahedron shares four edges with four neighboring octahedra to form an infinite needle-like chain [CuCl<sub>3</sub>]<sub>∞</sub>. The shortest intra-chain Cu–Cu distance is 3.460 (2) Å, while the two other contacts are about 3.9 and 4.05 Å. The geometric data of the inorganic fragment are tabulated in Table S2 (ESI<sup>†</sup>). 2-Amino-4-methylpyrimidinium is observed in its N1-protonated form. The C–C and C–N bond lengths do not allow for a distinction between single and double bond and range within 1.325(11) and 1.397(12) Å. These values are similar to reported structures, e.g. [C<sub>5</sub>H<sub>8</sub>N<sub>3</sub>]<sub>2</sub>ClSbCl<sub>4</sub>·H<sub>2</sub>O and C<sub>5</sub>H<sub>8</sub>N<sub>3</sub>H<sub>2</sub>PO<sub>4</sub>.<sup>44,45</sup> The short distance of 1.299(11) Å for the C1–N3 bond confirms the sp<sup>2</sup> hybridization of the exocyclic N3 nitrogen atom. The reduced basicity of the N3 nitrogen might favor the protonation at N1, similar to the compounds reported in the literature.<sup>46–49</sup> Within

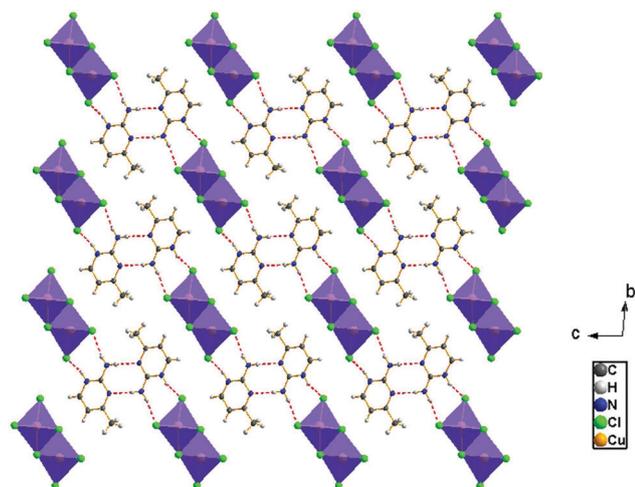


Fig. 3 Hydrogen bond networks of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  extended along  $[-211]$

the organic network, two pyrimidinium ions interact with each other *via* hydrogen bonds between  $\text{N}3\text{-H}3\text{NA}$  and  $\text{N}3$  with a  $\text{H}3\text{NA} \cdots \text{N}3$  distance of 2.16 Å. The organic cations are linked to the inorganic polymeric fragments *via* the  $\text{H} \cdots \text{Cl}$  bonds to lead to a linear hydrogen bond network extending along  $[-211]$  (Fig. 3). The geometric parameters of the hydrogen bonds are collated in Table S3 (ESI<sup>†</sup>). The  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  structure is considered as a 1D copper(II)-based perovskite.

### Infrared spectroscopy

The infrared spectrum of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  is based on the comparison with those of similar compounds reported in the literature, that contain the  $(\text{C}_5\text{H}_8\text{N}_3)^+$  cation.<sup>44</sup> Fig. 4 reports the presence of different bands cited below.

Two important bands at  $3310$  and  $3400 \text{ cm}^{-1}$  are attributed to the  $\text{NH}^+$  vibrations due to the protonation of the amine. The moderately intense bands appearing at  $3175$  and  $3092 \text{ cm}^{-1}$

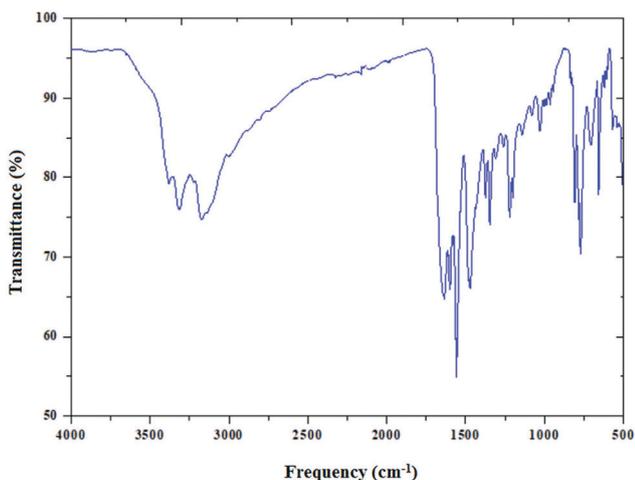


Fig. 4 The infrared absorption spectra of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$ , dispersed in a KBr pellet.

correspond to the  $\nu_{\text{C-H}}$  stretching vibration of the 2-amino-4-methyl pyrimidine group. In addition, the band corresponding to the  $\delta_{\text{as}}$  of  $(\text{CH}_3)$  is found at  $3002 \text{ cm}^{-1}$ . The asymmetric ( $\nu_{\text{as}}$ ) and the symmetric ( $\nu_{\text{s}}$ ) stretching vibrations of the  $\text{NH}_2$  group appear at  $1563 \text{ cm}^{-1}$  and  $1640 \text{ cm}^{-1}$ , respectively. The vibration of the double bond ( $\text{C}=\text{C}$ ) appears as two lines at  $1450$  and  $1600 \text{ cm}^{-1}$ . The peak at  $1463 \text{ cm}^{-1}$  is assigned to  $\nu_{\text{C-H}}$ . Also the two peaks around  $1343 \text{ cm}^{-1}$  and  $1222 \text{ cm}^{-1}$  are attributed to the  $\text{C-N}$  stretching vibration. Besides, the Off-plane deformation is displayed at  $770 \text{ cm}^{-1}$ . Eventually, the peak centered at  $682 \text{ cm}^{-1}$  is relative to the stirring of  $\text{NH}_2$ .

### Thermal analysis

In order to analyze the thermal stability of the synthesized compound, simultaneous TGA–DSC measurements were carried out (Fig. 5). To simplify the description of the degradation mechanism, we have chosen to discuss the decomposition of a cluster,  $(\text{C}_5\text{H}_8\text{N}_3)_2[\text{Cu}_2\text{Cl}_6]$ , containing two organic cations and an inorganic  $\text{Cu}_2\text{Cl}_6$  dimer. The Fig. 5 shows that the total degradation of the title compound occurs in two stages. The first one is observed between  $150$  and  $449 \text{ }^\circ\text{C}$  and corresponds to the departure of two organic cations. The second stage of weight loss observed between  $450$  and  $650$  results from the decomposition of the mineral moieties. As we can see in the TGA curve, the decomposition of the organic moieties occurs in three steps. As the degradation analysis is performed under  $\text{O}_2$  atmosphere, they can be attributed to the oxidation of organic matter and the gaseous products that arise during thermal decomposition. The obtained theoretical values suggest the departure of the carbon atoms in two different steps. The first step can be assigned to the oxidation of three carbons from the ring with the elimination of  $\text{CO}_2$  with mass loss of 11.84% (theor. 12.86%). The weight loss of 11.82% corresponds to the departure of the two remaining carbon atoms as  $\text{CH}_4$  gas (theor. 11.46%). The nitrogen atoms are probably oxidized into  $\text{NO}_2$  gas with weight loss of 13.8% (theor. 15%). During the

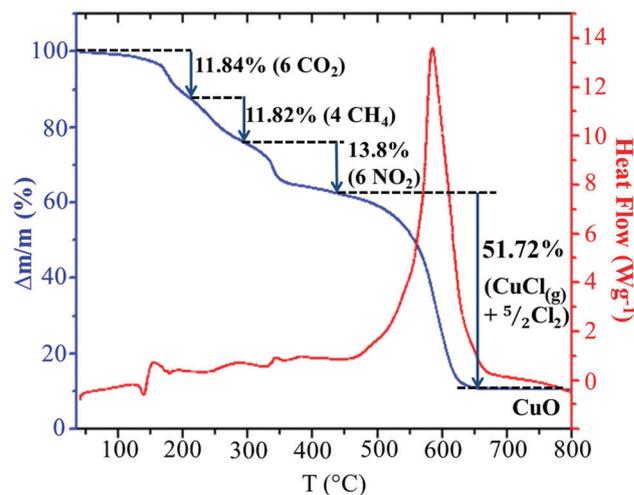


Fig. 5 Simultaneous TGA–DSC curves for the decomposition of the  $(\text{C}_5\text{H}_8\text{N}_3)_2[\text{Cu}_2\text{Cl}_6]$  cluster.

second stage of the degradation, the inorganic fragment  $\text{Cu}_2\text{Cl}_6$  is probably transformed into  $2\text{CuCl}_2$  after the departure of one  $\text{Cl}_2$ . As observed in the decomposition mechanism of  $\text{CuCl}_2$  solid under inert atmosphere,<sup>50</sup> the  $\text{CuCl}_2(\text{s})$  decompose into  $\text{CuCl}(\text{s})$  at  $455.5\text{ }^\circ\text{C}$  with the departure of  $1/2\text{ Cl}_2$  and the obtained  $\text{CuCl}(\text{s})$  melt at the same temperature. Then, a part of the  $\text{CuCl}(\text{liq})$  evaporate at  $488.5\text{ }^\circ\text{C}$ . The comparison of this mechanism with the experimental results suggests that the decomposition of the inorganic network is done according to the same mechanism up to the evaporation of a part of  $\text{CuCl}(\text{l})$ . As the analysis is done under  $\text{O}_2$  atmosphere, 10.76% of the final decomposition product is the corresponding metal oxide  $\text{CuO}$  (theor. 11.3%) obtained after the oxidation of the remaining  $\text{CuCl}(\text{l})$  and the elimination of  $1/2\text{ Cl}_2$ . Hence, the second decomposition stage accompanied by a weight loss of 51.72% is associated with the departure of  $\text{CuCl}(\text{g})$  and  $5/2\text{ Cl}_2$  gases (theor. 49.34%). This decomposition process is accompanied by a large endothermic peak on the DSC curve at about  $586\text{ }^\circ\text{C}$ .

### Optical properties

**UV-Vis-NIR diffuse reflectance spectroscopy.** Due to the interactions between radiations and the sample, a part of the incident beam will be absorbed, transmitted or reflected by the sample. The absorption of radiation in the visible range, from 400 to 800 nm, and in the ultraviolet range, between 190 and 400 nm,<sup>51</sup> causes electronic transitions and thus disturbances in the electronic structure of atoms, ions or molecules. For analyzing the electronic transitions within the structure, the Kubelka-Munk function (eqn (2)) is generally used to obtain the optical absorption (OA) spectra from the recorded diffuse reflectance.<sup>52,53</sup>

$$F(R) = (1 - R)^2/2R \quad (2)$$

where  $R$  is the absolute reflectance of the sample and  $F(R)$  is the so-called Kubelka-Munk absorption. The obtained OA spectrum, presented in Fig. 6(a), shows two broad bands where the

intense one is located in the wavelength region below 550 nm and the second band is observed around 803 nm.

Using the Tauc plot, the direct fundamental band gap, which corresponds to electron excitation from the valence band to the conduction band, was determined from the following relation:<sup>54</sup>

$$[F_{\text{KM}}(R) \times h\nu] = A_0(h\nu - E_g)^n$$

where  $h\nu$  is the incident photon energy and  $A_0$  is a material dependent constant and  $E_g$  is the optical band gap. The value of  $n$  depends on the nature of transition. It can take the value  $1/2$  when the transition is direct and 2 when the transition is indirect. As shown in the plot of  $[F(R) \times h\nu]^2$  as a function of photon energy  $h\nu$  (Fig. 6(b)), the band gap was extracted from the extrapolation of the linear part to the  $x$ -axis at  $[F(R) \times h\nu]^2 = 0$ . The direct gap energy is found to be 2.21 eV which is smaller than that of the one-dimensional  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$  (2.56 eV).<sup>27</sup>

As indicated in previously reported Cu-based materials,<sup>9,55,56</sup> the most energetic band corresponds to ligand to metal charge transfers (LMCT) from the p-orbitals of the  $\text{Cl}^-$  anions to the d-orbitals of the  $\text{Cu}^{2+}$  cations. The Gaussian fitting of the OA spectrum, plotted in Fig. 7, shows that the material exhibits five LMCT transitions. The lowest energetic band observed at 803 nm results from the crystal field transitions (CFT) within the  $\text{Cu}(\text{II})$  ions.<sup>57</sup> The shift of these transitions to low energy regions confirms the housing of the copper anions within octahedral elongated sites with a tetragonal symmetry  $D_{4h}$ .<sup>56</sup> This local deformation is the result of the high Jahn Teller effect around the d(Cu)-orbitals. Fig. 7 shows that this broad-band overlaps three d-d transition bands E1, E2 and E3 from the  $a_{1g}$ ,  $b_{2g}$  and  $e_g$  orbitals to the highest energetic level  $b_{1g}$ , respectively.<sup>9,56</sup> These bands are very intense, when compared to those of the one-dimensional  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$ ,<sup>27</sup> so that they overlap with the LMCT bands which make the material an excellent UV-Vis-NIR absorber and suitable for use in SC photovoltaic devices. With reference to  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$ , we list in Table 1 the assignments of the peaks observed below 550 nm to their corresponding LMCT transitions.

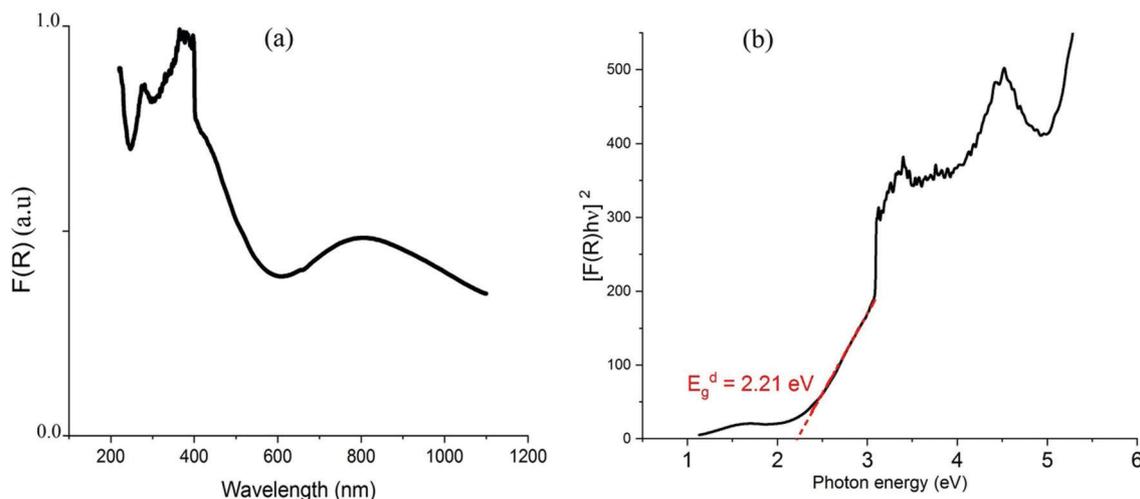


Fig. 6 Optical absorption spectrum (a) and Tauc plot of  $[F(R) \times h\nu]^2$  vs.  $h\nu$  (b).

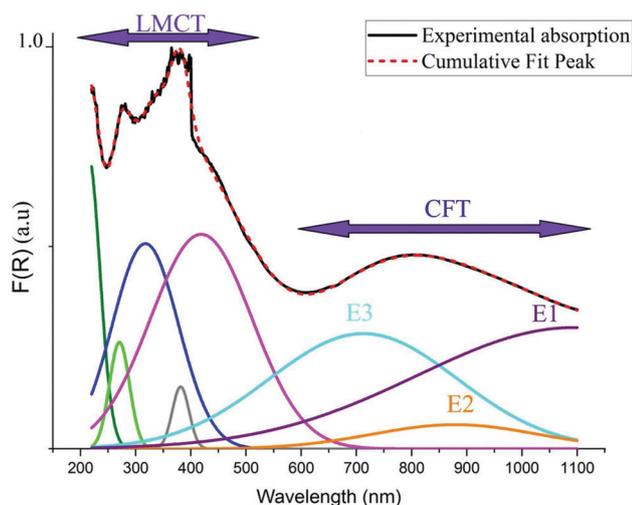


Fig. 7 Gaussian fitting of the OA spectrum of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$ .

**Table 1** Assignment of the observed LMCT transition (in nm) compared to those of  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$ .<sup>27</sup>

Assignment	Observed transition in $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$	Transition in $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$
$a_{2u}(\pi + \sigma) \rightarrow b_{1g}(x^2 - y^2)$	448	418
$e_u(\pi + \sigma) \rightarrow b_{1g}(x^2 - y^2)$	406	381
$b_{2u}(\pi) \rightarrow b_{1g}(x^2 - y^2)$	349	317
$e_u(\pi + \sigma) \rightarrow b_{1g}(x^2 - y^2)$	288	270
$e_u(\sigma + \pi) \rightarrow b_{1g}(x^2 - y^2)$	249	—
$a_{2u}(\sigma + \pi) \rightarrow b_{1g}(x^2 - y^2)$	—	213

**Computational modeling.** DFT simulations have been carried out to further analyze the structural and optical properties of the  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  complex, see Computational Details. Starting from the crystal structure, we carried out hybrid geometry optimization obtaining a good agreement with the experimental measurements. In particular we found the Cu–Cl equatorial distance in a range of 2.25–2.29 Å and the axial Cu–Cl distance in a range between 3.07 and 3.11 Å. Moving to the analysis of the electronic properties, we have shown the density of states (DOS) in Fig. 8. To further analyze the role of the Cu coordination geometry and the organic cation in affecting the electronic structure, we compare the DOS of the  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  complex with that of the previously studied  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$  species in ref. 27. Since  $\text{Cu}^{2+}$  is expected to show an unpaired electron, spin polarized calculations have been performed and the relative contributions of the spin-up and -down components are reported as positive and negative values, respectively.

As we can see from the DOSs in Fig. 8, the calculated HOMO<sub>x</sub>–LUMO<sub>β</sub> band gap of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  is 2.5 eV and it is 0.2 eV lower than the previous simulated band gap of  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$  (2.7 eV).<sup>27</sup> Both calculated values slightly overestimate the experimental measurements (2.21 and 2.56 eV,<sup>27</sup> respectively) but calculation accurately reproduces the relative difference.

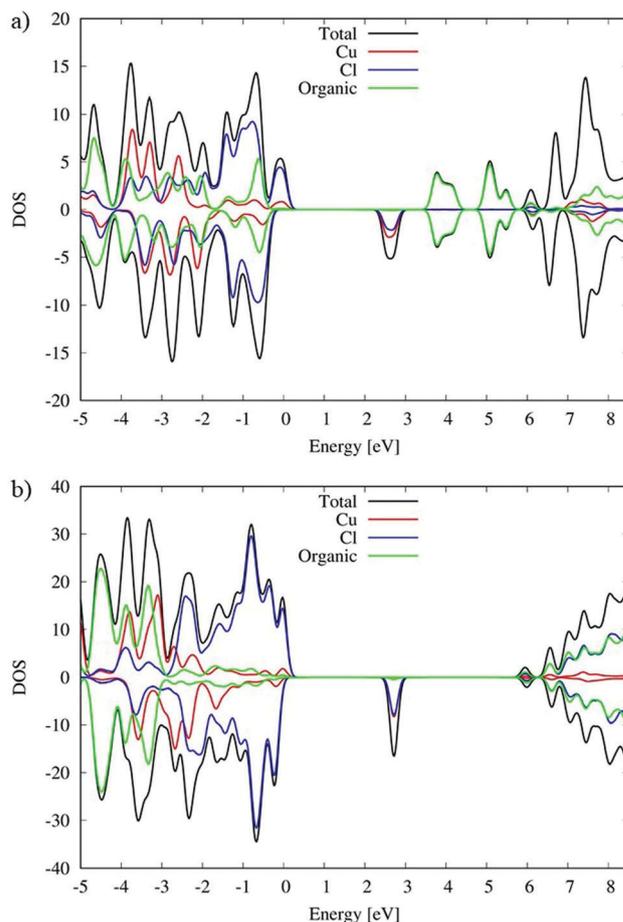


Fig. 8 DOS of (a)  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  and (b)  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$ .

The VB and CB nature of the two different species are similar, and in particular, the main contribution to the VB is associated with the Cl species mixed with a Cu contribution while the first unoccupied band is mainly associated with Cu with a lower Cl contribution.

However, the contribution of the organic molecules is different. For the  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$  species the organic molecules in green, see Fig. 8(b), show the intense signal of their HOMO<sub>x</sub> 3 eV below the VB edge and the signal of their LUMO<sub>β</sub> 6 eV above the VB edge of the systems. This is expected due to the aliphatic nature of the organic cation. Moving to the  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  species, the conjugated character of the organic molecules induces a different alignment between the inorganic and organic material partial density of states (PDOS) contributions. In particular, in that case (Fig. 8(a)) the organic contribution to the VB in green is close to the edges lying only 0.5 eV below. A similar situation is retrieved for the CB, where the organic contribution is 1.1 eV above the CB edge. This role of the organic cation implies a higher electronic coupling between the organic and inorganic frameworks of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  with respect to  $(\text{C}_5\text{H}_{14}\text{N}_2)[\text{CuCl}_4]$  that could in principle increase the electronic transport, charge transfer and charge hopping upon photo-excitation, as already proposed in our previous papers.<sup>58</sup>

## Magnetic properties

The magnetic properties of  $(C_5H_8N_3)[CuCl_3]$  are governed by the magneto-structural correlations within polymeric chains formed by  $[Cu_2Cl_6]$  units along the  $a$ -axis, separated by the 2-amino-4-methylpyrimidinium cations, and this structural motive resembles a frustrated spin ladder. The six chlorine atoms in the structure octahedrally coordinate each  $Cu^{2+}$  ion. The Jahn-Teller effect leads to the elongation of the octahedron, as shown in Fig. 2(b). In this case, the single unpaired electron resides in the  $d_{x^2-y^2}$  orbital with its lobes oriented in the equatorial plane of the elongated bipyramid. This configuration leads to an effective overlap of the  $d_{x^2-y^2}$  orbitals between the two closest  $Cu^{2+}$  ions with 3.46 Å separation shown in Fig. 2, and a strong exchange interaction is expected between them (dimers forming ladder rungs). On the other hand, the interaction between these copper dimers is expected to be weak along the  $a$ -axis. The exchange interactions can also be evaluated using the results of Hatfield and Hodgson *et al.*,<sup>59</sup> who studied a series of bichloride bridged  $Cu^{2+}$  dimers. The ratio of the bridging Cu-Cl-Cu angle and the longer Cu-Cl distance  $\Phi/R$  correlate structural features with the expected exchange interactions. Indeed, the parameter  $\Phi/R = 42.18 \text{ \AA}^{-1}$  corresponding to a strong antiferromagnetic (AFM) exchange interaction of about  $-144 \text{ K}$  is found for a  $Cu^{2+}$  pair on the rungs. For a pair of  $Cu^{2+}$  ions along the legs of the ladder (separated by a distance of 3.9 Å), the parameter  $\Phi/R = 31.4 \text{ \AA}^{-1}$  and negligible exchange interaction are expected. Two possible values of  $\Phi/R$ ,  $31.3 \text{ \AA}^{-1}$  and  $29.7 \text{ \AA}^{-1}$ , can be estimated for a pair of  $Cu^{2+}$  ions separated by the distance of 4.5 Å (Fig. 2(c)) suggesting the presence of a negligible or a weak AFM interaction of about  $-10 \text{ K}$ .


In addition, we have performed a simple BS DFT calculation using the ORCA package with the B3LYP exchange–correlation functional to estimate possible exchange interactions. A fragment of the ladder structure was selected; non-magnetic  $Zn^{2+}$  ions replaced all  $Cu^{2+}$  ions except for two selected  $Cu^{2+}$  ions in the center of the fragment representing a pair for the BS DFT calculation. For the rung exchange interaction a fragment of 3 rungs and for the leg and frustrating exchange interaction a fragment of 4 rungs were selected as shown in Fig. S2 (ESI<sup>†</sup>). The results are summarized together with magneto-structural correlations in Table 2. The results clearly indicate strong AFM dimers on the rungs of the ladder structure. At the same time, other interactions seem to be negligible, spanning the range of small AFM or ferromagnetic (FM) values.

The analysis of magneto-structural correlation and BS DFT calculations thus indicates that  $(C_5H_8N_3)[CuCl_3]$  can be described as a system of weakly interacting  $S = 1/2$  AFM dimers or an exchange alternating  $S = 1/2$  AFM chain (or, in other terms, dimerized AFM chain). The temperature dependence of the susceptibility measured in the temperature range of 4.2–300 K shown in Fig. 9 is characterized by a maximum at  $T = 76 \text{ K}$  compatible with the proposed AFM models. A Curie-like tail at the lowest temperatures most probably originates from intrinsic impurities often observed in dimerized AFM

**Table 2** Comparison of estimated exchange interaction from the BS DFT calculations, magneto-structural correlations, and experiment for  $(C_5H_8N_3)[CuCl_3]$

Copper pair	$2J_{BS}/k_B$ (K) DFT	BS $\Phi/R$ ( $\text{\AA}^{-1}$ )	$J/k_B$ (K)	$J/k_B$ (K) Experiment
Cu–Cu 3.46 Å, rung	–126.7	42.18	–144	–122.7 <sup>a</sup>
Cu–Cu 3.9 Å, leg	1.23	31.4	0	
Cu–Cu 4.5 Å, frustration	1.58	31.3, 29.7	0, –14	–33 <sup>b</sup>

<sup>a</sup>  $S = 1/2$  AFM dimer model. <sup>b</sup> Using exchange alternating  $S = 1/2$  AFM chain model.

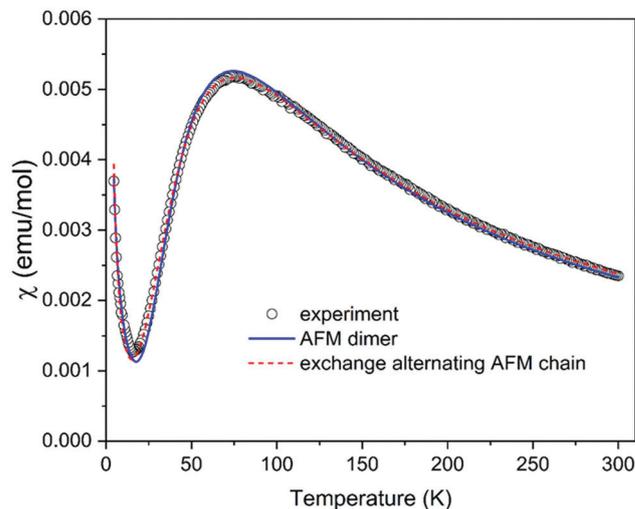

**Fig. 9** Temperature dependence of the susceptibility of  $(C_5H_8N_3)[CuCl_3]$ , estimated as the ratio of the measured magnetic moment and applied magnetic field 1 kOe including the fits using models described in the text.

systems as a signature of the fragmentation. The experimental data were first analyzed using a simple model of  $S = 1/2$  AFM dimers described by the well-known Bleaney–Bowers formula,<sup>60</sup> including a Curie contribution in the form  $\chi = (1 - 2\rho)\chi_{\text{dimer}} + \rho\chi_{\text{Curie}}$ , where  $\rho$  represents the concentration of paramagnetic spins. The spin dimer model is described by the Hamiltonian in the form  $\hat{H}_{\text{dimer}} = -J\hat{S}_1\hat{S}_2$ . The fit yielded the exchange interaction within dimer  $J/k_B = -122.7 \text{ K}$ ,  $g$ -factor  $g = 2.11$ , and  $\rho = 0.04$  in a good agreement with the values suggested from magneto-structural correlations. To fit the susceptibility using high-temperature series expansion (HTSE) formulas for an AFM spin ladder<sup>61,62</sup> or exchange alternating AFM chain<sup>63</sup> might be tricky for the present data, since HTSE works well only at temperatures  $k_B T/J > 0.25$ . Since the model of exchange alternating AFM chain is more appropriate here, as suggested from the previous discussion, we tried to use the HTSE formula proposed by Hatfield,<sup>63</sup> including Curie contribution in the form  $\chi = (1-2\rho)\chi_{\text{alterchain}} + \rho\chi_{\text{Curie}}$ . The fit yields  $J/k_B = -125.2 \text{ K}$ , alternation parameter  $\alpha = 0.265$ ,  $g = 2.18$ , and  $\rho = 0.043$  with the curve almost indistinguishable from the spin dimer model. The alternation parameter may be overestimated in this case due to the lower accuracy of the model at low temperatures.

Our attempt to fit the spin ladder model with  $J_{\text{rung}} = J$  and  $J_{\text{leg}}$  resulting from the studies of Gu *et al.*<sup>64</sup> and Landee<sup>65</sup> (valid for  $J_{\text{leg}}/J_{\text{rung}} < 0.1$ ) indeed yields negligible  $J_{\text{leg}} = 0$  with  $J_{\text{rung}}/k_{\text{B}} = -122.7$  K,  $g = 2.11$ , and  $\rho = 0.04$  identical to the simple  $S = 1/2$  AFM dimer model. In summary, despite the ladder-like arrangement of the  $\text{Cu}^{2+}$  ions, the magnetic properties of  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  are best described by the model of  $S = 1/2$  AFM dimers with  $J/k_{\text{B}} = -122.7$  K.

## Conclusion

In summary, a 1D lead-free hybrid perovskite based on copper  $(\text{C}_5\text{H}_8\text{N}_3)[\text{CuCl}_3]$  was successfully fabricated. Optical characterization studies show that, due to the Jahn Teller effect, the CFT improve the absorption behaviors of the material in the visible region. The theoretical DFT calculation of the electronic structure demonstrates that the use of a conjugated cation enhances the electronic transport, the charge transfer and charge hopping upon photo-excitation. The good agreement between the experimental and the theoretical results reveals the semiconducting properties of the material with a fundamental energy gap of 2.21 eV. Therefore, thanks to the intense LMCT transitions and CFT, in the presence of aromatic organic rings, this new material can be suitable for green SCs application as a good UV-Vis-NIR absorber. The magnetic properties of the investigated material are described by the model of  $S = 1/2$  AFM dimers with  $J/k_{\text{B}} = -122.7$  K.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors extend their appreciation to the Deputyship for Research & Innovation, Ministry of Education in Saudi Arabia for funding this work through the project number "375213500". The authors would like to extend their sincere appreciation to the central laboratory at Jouf University for supporting this study. E. Č. and M. H. were supported by the Scientific Grant Agency of Ministry of Education, Science, Research and Sport of the Slovak Republic under contract No. VEGA 1/0426/19 and Slovak Research and Development Agency under contract No. APVV SK-BY-RD-19-0008 and APVV-18-0197.

## Notes and references

- 1 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, 6050–6051.
- 2 T. M. Koh, K. Fu, Y. Fang, S. Chen, T. C. Sum, N. Mathews, S. G. Mhaisalkar, P. P. Boix and T. Baikie, *J. Phys. Chem. C*, 2014, 118, 16458–16462.
- 3 A. Babayigit, A. Ethirajan, M. Muller and B. Conings, *Nat. Mater.*, 2016, 15, 247–251.
- 4 B. Conings, J. Drijkoningen, N. Gauquelin, A. Babayigit, J. D'Haen, L. D'Olieslaeger, A. Ethirajan, J. Verbeeck, J. Manca, E. Mosconi, F. De Angelis and H. G. Boyen, *Adv. Energy Mater.*, 2015, 5, 1–8.
- 5 T. Leijtens, G. E. Eperon, N. K. Noel, S. N. Habisreutinger, A. Petrozza and H. J. Snaith, *Adv. Energy Mater.*, 2015, 5, 1–23.
- 6 C. C. Stoumpos, L. Frazer, D. J. Clark, Y. S. Kim, S. H. Rhim, A. J. Freeman, J. B. Ketterson, J. I. Jang and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2015, 137, 6804–6819.
- 7 B. W. Park, B. Philippe, X. Zhang, H. Rensmo, G. Boschloo and E. M. J. Johansson, *Adv. Mater.*, 2015, 27, 6806–6813.
- 8 K. Nishimura, M. A. Kamarudin, D. Hirotsu, K. Hamada, Q. Shen, S. Iikubo, T. Minemoto, K. Yoshino and S. Hayase, *Nano Energy*, 2020, 74, 104858.
- 9 D. Cortecchia, H. A. Dewi, J. Yin, A. Bruno, S. Chen, T. Baikie, P. P. Boix and M. Gra, *Inorg. Chem.*, 2016, 55, 1044–1052.
- 10 L. Lanzetta, T. Webb, N. Zibouche, X. Liang, D. Ding, G. Min, R. J. E. Westbrook, B. Gaggio, T. J. Macdonald, M. S. Islam and S. A. Haque, *Nat. Commun.*, 2021, 12, 2853.
- 11 C. Li, X. Lu, W. Ding, L. Feng, Y. Gao and Z. Guo, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2008, 64, 702–707.
- 12 C. Li, K. C. K. Soh and P. Wu, *J. Alloys Compd.*, 2004, 372, 40–48.
- 13 J. Yin, H. Li, D. Cortecchia, C. Soci and J. L. Brédas, *ACS Energy Lett.*, 2017, 2, 417–423.
- 14 A. Yanguí, S. Pillet, E. E. Bendeif, A. Lussou, S. Triki, Y. Abid and K. Boukheddaden, *ACS Photonics*, 2018, 5, 1599–1611.
- 15 S. Huang, G. Tang, H. Huang, X. Gang Wu, P. Zhou, L. Zou, L. Xie, J. Deng, X. Wang, H. Zhong and J. Hong, *Sci. Bull.*, 2018, 63, 1254–1259.
- 16 M. E. Kamminga, M. Azhar, J. Zeisner, A. M. C. Maan, B. Büchner, V. Kataev, J. Baas, G. R. Blake, M. Mostovoy and T. T. M. Palstra, *Phys. Rev. Mater.*, 2018, 2, 1–7.
- 17 M. Abid Derbel, M. M. Turnbull, H. Naïli and W. Rekik, *Polyhedron*, 2020, 175, 114220.
- 18 X. Li, X. Zhong, Y. Hu, B. Li, Y. Sheng, Y. Zhang, C. Weng, M. Feng, H. Han and J. Wang, *J. Phys. Chem. Lett.*, 2017, 8, 1804–1809.
- 19 X. P. Cui, K. J. Jiang, J. H. Huang, Q. Q. Zhang, M. J. Su, L. M. Yang, Y. L. Song and X. Q. Zhou, *Synth. Met.*, 2015, 209, 247–250.
- 20 L. Xie, B. Chen, F. Zhang, Z. Zhao, X. Wang, L. Shi, Y. Liu, L. Huang, R. Liu, B. Zou and Y. Wang, *Photonics Res.*, 2020, 8, 768.
- 21 F. Zhang, Z. Zhao, B. Chen, H. Zheng, L. Huang, Y. Liu, Y. Wang and A. L. Rogach, *Adv. Opt. Mater.*, 2020, 8, 1901723.
- 22 Z. Guo, J. Li, R. Pan, J. Cheng, R. Chen and T. He, *Nanoscale*, 2020, 12, 15560–15576.
- 23 X. Li, B. Li, J. Chang, B. Ding, S. Zheng, Y. Wu, J. Yang, G. Yang, X. Zhong and J. Wang, *ACS Appl. Energy Mater.*, 2018, 1, 2709–2716.
- 24 K. Ahmad and S. M. Mobin, *Energy Technol.*, 2020, 8, 1901185.

- 25 A. M. Elseman, A. E. Shalan, S. Sajid, M. M. Rashad, A. M. Hassan and M. Li, *ACS Appl. Mater. Interfaces*, 2018, **10**, 11699–11707.
- 26 R. Valiente and F. Rodriguez, *ACS Appl. Mater. Interfaces*, 2020, **12**, 37807–37810.
- 27 M. Bourwina, R. Msalmi, S. Walha, M. M. Turnbull, T. Roisnel, F. Costantino, E. Mosconi and H. Naïli, *J. Mater. Chem. C*, 2021, **9**, 5970–5976.
- 28 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 1990, **A46**, 467–473.
- 29 G. Sheldrick, *SHELX-97 Programs Cryst. Struct. Anal.*, University of Göttingen, Göttingen, Germany, 1997.
- 30 P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. De Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari and R. M. Wentzcovitch, *J. Phys.: Condens. Matter*, 2009, **21**, 395502.
- 31 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 32 J. Heyd, G. E. Scuseria and M. Ernzerhof, *J. Chem. Phys.*, 2003, **118**, 8207–8215.
- 33 H. Nagao, M. Nishino, Y. Shigeta, T. Soda, Y. Kitagawa, T. Onishi, Y. Yoshioka and K. Yamaguchi, *Coord. Chem. Rev.*, 2000, **198**, 265–295.
- 34 F. Neese, F. Wennmohs, U. Becker and C. Riplinger, *J. Chem. Phys.*, 2020, **152**, 224108.
- 35 V. N. Staroverov, G. E. Scuseria, J. Tao and J. P. Perdew, *J. Chem. Phys.*, 2003, **119**, 12129–12137.
- 36 K. Yamaguchi, Y. Takahara and T. Fueno, in *Applied Quantum Chemistry*, Springer, Netherlands, Dordrecht, 1986, pp. 155–184.
- 37 C. Van Wüllen, *J. Chem. Phys.*, 1998, **109**, 392–399.
- 38 E. Van Lenthe, E. J. Baerends and J. G. Snijders, *J. Chem. Phys.*, 1993, **99**, 4597–4610.
- 39 D. A. Pantazis, X. Y. Chen, C. R. Landis and F. Neese, *J. Chem. Theory Comput.*, 2008, **4**, 908–919.
- 40 A. Schäfer, C. Huber and R. Ahlrichs, *J. Chem. Phys.*, 1994, **100**, 5829–5835.
- 41 F. Neese, F. Wennmohs, A. Hansen and U. Becker, *Chem. Phys.*, 2009, **356**, 98–109.
- 42 F. Weigend, *Phys. Chem. Chem. Phys.*, 2006, **8**, 1057–1065.
- 43 A. Hellweg, C. Hättig, S. Höfener and W. Klopper, *Theor. Chem. Acc.*, 2007, **117**, 587–597.
- 44 Z. Aloui, M. Essid, S. Abid, M. Rzaigui and C. Ben Nasr, *Monatsh. Chem.*, 2015, **146**, 1465–1471.
- 45 S. P. Thomas and J. Sunkari, *Acta Crystallogr., Sect. E: Struct. Rep. Online*, 2013, **69**(Pt 4), o529, DOI: 10.1107/S160053681300648X.
- 46 N. Hfidhi, N. Krayem, J. Erwann, T. Bataille and H. Naïli, *J. Inorg. Organomet. Polym. Mater.*, 2021, **31**, 1549–1564.
- 47 N. Mhadhbi, S. Saïd, S. Elleuch, T. Lis and H. Naïli, *J. Mol. Struct.*, 2016, **1105**, 16–24.
- 48 P. Panneerselvam, P. T. Muthiah and S. Francis, *Acta Crystallogr., Sect. E: Struct. Rep. Online*, 2004, **60**, o747–o749.
- 49 J. N. Low, D. Cannon, A. Quesada, A. Marchal, M. Melguizo, M. Nogueras, A. Sánchez and C. Glidewell, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.*, 2001, **57**, 604–607.
- 50 S. Zhou, S. Shen, D. Zhao, Z. Zhang and S. Yan, *J. Therm. Anal. Calorim.*, 2017, **129**, 1445–1452.
- 51 E. Frank and A. Settle, 1997.
- 52 C. Aydn, M. S. Abd El-Sadek, K. Zheng, I. S. Yahia and F. Yakuphanoglu, *Opt. Laser Technol.*, 2013, **48**, 447–452.
- 53 C. C. B. Philips-Invernizzi and D. Dupont, *Opt. Eng.*, 2001, **40**, 1082.
- 54 M. Duvenhage, M. Ntwaeaborwa, H. G. Visser, P. J. Swarts, J. C. Swarts and H. C. Swart, *Opt. Mater.*, 2015, **42**, 193–198.
- 55 M. Bochalya, P. K. Kanaujia, G. V. Prakash and S. Kumar, *J. Solid State Chem.*, 2019, **273**, 219–225.
- 56 R. Valiente and F. Rodriguez, *J. Phys. Chem. Solids*, 1996, **57**, 571–587.
- 57 P. K. Olshin, O. S. Myasnikova, M. V. Kashina, A. O. Gorbunov, N. A. Bogachev, V. O. Kompanets, S. V. Chekalin, S. A. Pulkin, V. A. Kochemirovsky, M. Yu and A. S. Mereshchenko, *Chem. Phys.*, 2018, **503**, 14–19.
- 58 N. Marchal, E. Mosconi, G. García-Espejo, T. M. Almutairi, C. Quarti, D. Beljonne and F. De Angelis, *J. Phys. Chem. Lett.*, 2021, **12**, 2528–2535.
- 59 W. E. Marsh, K. C. Patel, W. E. Hatfield and D. J. Hodgson, *Inorg. Chem.*, 1983, **22**, 511–515.
- 60 B. Bleaney and K. D. Bowers, *Proc. R. Soc. London, Ser. A*, 1952, **214**, 451–465.
- 61 Z. Weihong and R. R. P. Singh, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1997, **55**, 8052–8055.
- 62 D. C. Johnston, M. Troyer, S. Miyahara, D. Lidsky, K. Ueda, M. Azuma, Z. Hiroi, M. Takano, M. Isobe, Y. Ueda, M. A. Korotin, V. I. Anisimov, A. V. Mahajan and L. L. Miller, 2000.
- 63 J. W. Hall, W. E. Marsh, R. R. Weller and W. E. Hatfield, *Inorg. Chem.*, 2002, **20**, 1033–1037.
- 64 Q. Gu, D.-K. Yu and J.-L. Shen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **60**, 3009.
- 65 C. P. Landee, M. M. Turnbull, C. Galeriu, J. Giantsidis and F. M. Woodward, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2001, **63**, 4.