



Cite this: *RSC Adv.*, 2021, 11, 19705

Received 26th February 2021
Accepted 5th May 2021

DOI: 10.1039/d1ra01563j

rsc.li/rsc-advances

ZnO nanowire embedded TiO₂ film as an electrode for perovskite CsPbI₂Br solar cells

Liqu Zheng,^a Gabrielle Page^a and Zhongrui Li^b

A comparative study was conducted to look into the impact of various electron transporting films on the performance of perovskite CsPbI₂Br solar cells. The solar cells with ZnO nanowires embedded TiO₂ as an electrode outperformed those with pure TiO₂ or pure ZnO. The enhanced performance is ascribed to the synergetic effect of both TiO₂/ZnO constituent properties. In particular, an appropriate amount of ZnO nanowires embedded in TiO₂ films could optimize the properties of the electron transporting layer by improving electron transport, light harvesting, and overall photovoltaic performance, leading to the power conversion efficiency as high as 10.53%.

Introduction

The meteoric rise of perovskite solar cells has witnessed the power conversion efficiency (PCE) soaring from 3.8% to the currently certified 25.2% (ref. 1 and 2) in single-junction architectures since 2009,³ attracting tremendous attention in both academic and industrial fields. In order to achieve the photovoltaic effect, the n-i-p heterojunction is conventionally constructed with a light absorbing perovskite layer (an intrinsic layer) being sandwiched by carrier selective or electron (n-layer)/hole (p-layer) layers, which, in turn, must energetically match the absorber layer. As far as the electron-selective layer (also called electron transporting layer (ETL)) is concerned, the conduction band edge is required to be lower than that of the perovskite layer for efficient charge injection while its valence band edge must be lower than the valence band edge of the perovskite layer to block the holes. The bandgap alignment of n-i-p layers would dynamically facilitate the “heavier” electrons rolling down and the “lighter” holes bubbling up, paving the way for photocurrent being readily extracted out of the devices.⁴ Meanwhile, carrier transport materials are supposed to possess high transparency in the optical spectrum while maintaining good carrier conductivity. These requirements must be fulfilled in order to not compromise the device efficiency, which constrains the material options of desirable charge selective contacts.

Semiconducting metal oxides have found widespread applications in optoelectronic devices due to their proper band gaps, ideally optical transparent, high electron mobility, excellent chemical stability, and so on.^{5–7} They play a vital role in device functioning, controlling the energy alignment and eventual

charge transfer. Among them, the d-block binary metal oxides like TiO₂ and ZnO, stand out as good candidate materials for photoelectrodes because of their dissimilarity in orbitals constituting their conduction band and valence band, which can ensure the effective charge separation and transportation generated in the intrinsic layer.⁸ For instance, the conduction

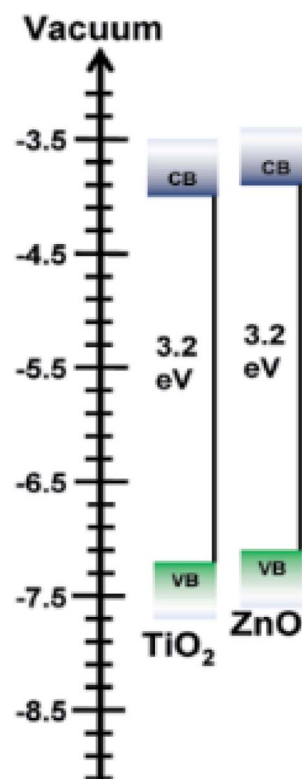


Fig. 1 Schematic diagram for the energy levels of the conduction and valence band of TiO₂ and ZnO Taken from ref. 5–7.

^aMath, Computer Science and Physics Department, Albany State University, Albany, GA31707, USA. E-mail: Liqu.zheng@asurams.edu

^bElectron Microbeam Analysis Laboratory, University of Michigan, Ann Arbor, MI48109, USA



band (CB) and valence (VB) energies of TiO_2 and ZnO are sketched in Fig. 1. Apparently, as semiconductors with similar wide band gaps, the conduction band edges of TiO_2 and ZnO are located at approximately the same level. Due to their excellent semiconducting properties, TiO_2 and ZnO have been widely adopted as electron transporting materials in photovoltaic field.^{9–12} For instance, the hybrid films of ZnO nanowires and TiO_2 have been reported as electrodes in dye-sensitized solar cells (DSSCs) which could enhance the efficiency by 26.9% compared with that of solar devices merely based on TiO_2 .^{13,14} The outstanding power conversion efficiency has been achieved not only because their bandgaps could perfectly align with absorbing layers, but also the composite films could considerably boost the light harvesting.^{15,16} In spite of their popularity in DSSCs, to our best knowledge, no research has yet been reported on the hybrid films of ZnO nanowires and TiO_2 nanoparticles as electrodes applied in the newly emerging perovskite solar cells. For the first time, the electrodes of ZnO nanowires embedded TiO_2 hybrid films will be attempted to explore the performance as ETL in mixed halide perovskite CsPbI_2Br solar cells.

In spite of the competitive efficiency of the organic–inorganic hybrid perovskite solar cells, the device hardly maintain integrity and functionality when exposed to the surroundings. Cesium (Cs) has been attempted to take the place of CH_3NH_3 (MA) to form all-inorganic halide perovskites CsPbX_3 ($\text{X} = \text{Cl}, \text{Br}, \text{I}$) to realize relatively long stability. Perovskites CsPbX_3 have found widespread applications in photo-electrics devices,^{17,18} due to the meritorious attributes like strong air/thermal stability, high light absorption coefficients, and phenomenal charge transporting with a reasonably long exciton diffusion length. Moreover, low temperature/cost ease solution processability allows for roll-to-roll manufacturing with flexible substrates.¹⁹ However, some issues still exist. A wide bandgap of 2.3 eV of CsPbBr_3 limits its absorption, thus the best performance only with 10.6%. Despite an ideal bandgap of 1.73 eV, α - CsPbI_3 (cubic phase) is merely stable at high temperature ($>300^\circ\text{C}$) and would become undesirable δ - CsPbI_3 (non-perovskite phase) under ambient conditions.²⁰ It would be hard to fabricate α - CsPbI_3 based solar cells under the routine conditions. CsPbI_2Br with a band gap of 1.91 eV, through partially substituting iodide (I) with bromide (Br)^{21,22} to tune the tolerance factor of perovskite structure, acts as a light absorber to improve overall device performance. In this work, a comparative study has been systematically conducted to investigate and evaluate the performance of ZnO , TiO_2 and TiO_2/ZnO as an electrode in perovskite CsPbI_2Br solar cells.

Experimental section

Zinc acetate dihydrate ($\text{Zn}(\text{O}_2\text{CCH}_3)_2$, 99.0%) served as a precursor to synthesize ZnO nanowires. 0.5 g of the precursor was placed in an alumina crucible, covered by an alumina lid, and then placed in a furnace. The crucible was heated to 300°C and held for a period of 1–12 hours, producing ZnO nanowires with different qualities in a powdery form.²³ By following different mass ratios, as-obtained ZnO and as-purchased TiO_2 (99.99%) powder were thoroughly

mixed up and put into dimethyl formamide (DMF) to make into solutions for developing films later on.

The perovskite precursor solution was prepared by dissolving as-purchased CsBr ($\geq 99.5\%$) and PbI_2 ($\geq 99.99\%$) at a 1 : 1 molar ratio into a mixture of solvents with dimethyl sulfoxide (DMSO)/DMF ratio at 2 : 3 (improving the crystallization, exhibiting the least number of defects and forming the final pin-hole free films²⁴) to make a solution with a concentration of $\sim 0.33 \text{ mol L}^{-1}$. The solution was kept stirring overnight in an N_2 -filled glove box. For further characterization, the solution was dried at 100°C for 10 min under nitrogen (N_2) to evaporate the solvent.²⁵

ITO glasses were cleaned by washing/rinsing with detergent and DI water. They were further cleaned by sonicating in acetone, and isopropanol for 10 min sequentially. After being thoroughly cleaned, the ITO glasses were dried in an oven with 100°C . Before constructing solar cells, the ITO glass was treated with oxygen plasma for 2 min. The TiO_2/ZnO solution with various ratios was spin-coated onto the treated ITO with a speed of 3000 rpm for 20 seconds as electron transporting layers. The as-prepared ITO/ TiO_2/ZnO substrates were placed into an N_2 -filled glovebox. The perovskite active layers were deposited onto the ITO/ TiO_2/ZnO substrates by spin-coating 30 seconds with speeds of

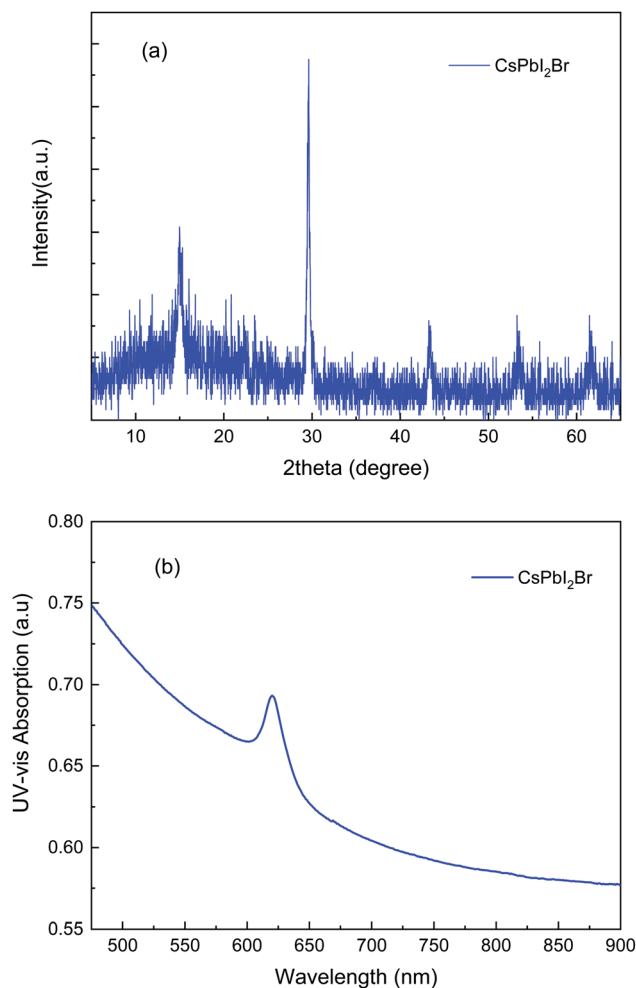


Fig. 2 (a) XRD profile and (b) UV-vis absorption spectrum for CsPbI_2Br .



2000 rpm and 5000 rpm, respectively. Annealing with temperature of 100 °C was conducted for 10 minutes to obtain a CsPbI₂Br film. Another batch of pre-cleaned ITO glasses was dip-coated with a carbon solution as the hole transporting layers. The solar cells were constructed by sandwiching perovskite covered ITO/TiO₂/ZnO substrates and carbon blanketed ITO glasses.

Morphology was examined by scanning electron microscopy (JEOL JSM-IT800 FE-SEM). UV-vis optical absorption spectra were recorded in an absorbance mode on a Varian Cary Bio 50 UV-visible spectrophotometer. X-ray diffraction patterns were collected on a Rigaku Ultima IV diffractometer in a grazing incident mode with an incident angle of 0.5°. Cu K-alpha line ($\lambda = 154.059$ pm) was utilized as a light source. The current density–voltage characteristic curves both in the dark and under AM1.5 illumination (100 mW cm⁻²) were recorded by a Keithley 2400 source meter, in which current was continuously measured as a function of voltage with a step of 0.02 V. The power conversion efficiency of the devices were measured from an area of 1 × 1 cm² under a small-area class-B solar simulator (PV Measurements, Inc.).

Results and discussions

The X-ray diffraction profile of the intrinsic light absorber CsPbI₂Br was collected in a speed mode as shown in Fig. 2a. A

single α black phase was detected, reflected by two strong diffraction peaks located at 14.9° and 30.0°, corresponding to the α phase of Cs_{1-x}FA_xPbI₂Br.^{20,26} The ultraviolet-visible absorption spectroscopy, as presented in Fig. 2b, further confirmed that the perovskite film of CsPbI₂Br was formed, identified by a strong absorbing peak at about 627 nm wavelength corresponding to an optical bandgap of 1.91 eV. Both XRD profile and UV-vis absorption results are consistent with the previous reports.^{27,28}

Scanning electron microscopy images in Fig. 3 disclose the morphology of various electron transporting films. Fig. 3a reveals that ZnO nanowires were randomly matted on the ITO glass. The nanowires with high quality and high purity were distributed forming a net-like film with up to a few micrometers in length, about 40–60 nanometers in diameter. As purchased TiO₂ nanoparticles were uniformly deposited and randomly connected on the substrate, as scrutinized in Fig. 3b, without any particular eye-striking feature. Fig. 3c and d suggest that the film with a TiO₂/ZnO ratio at 99 : 1 shared the morphology similar to that of the one with a ratio of 97 : 3, so does the SEM of the film with 95 : 5 (not shown). Few random ZnO nanowires were decorated here or there on the very top surface. Network of ZnO nanowires was embedded in the film, which was revealed by the top topography as indicated by arrows. Due to the large amount in the solution, the film feature of TiO₂ dominates on the surface area.

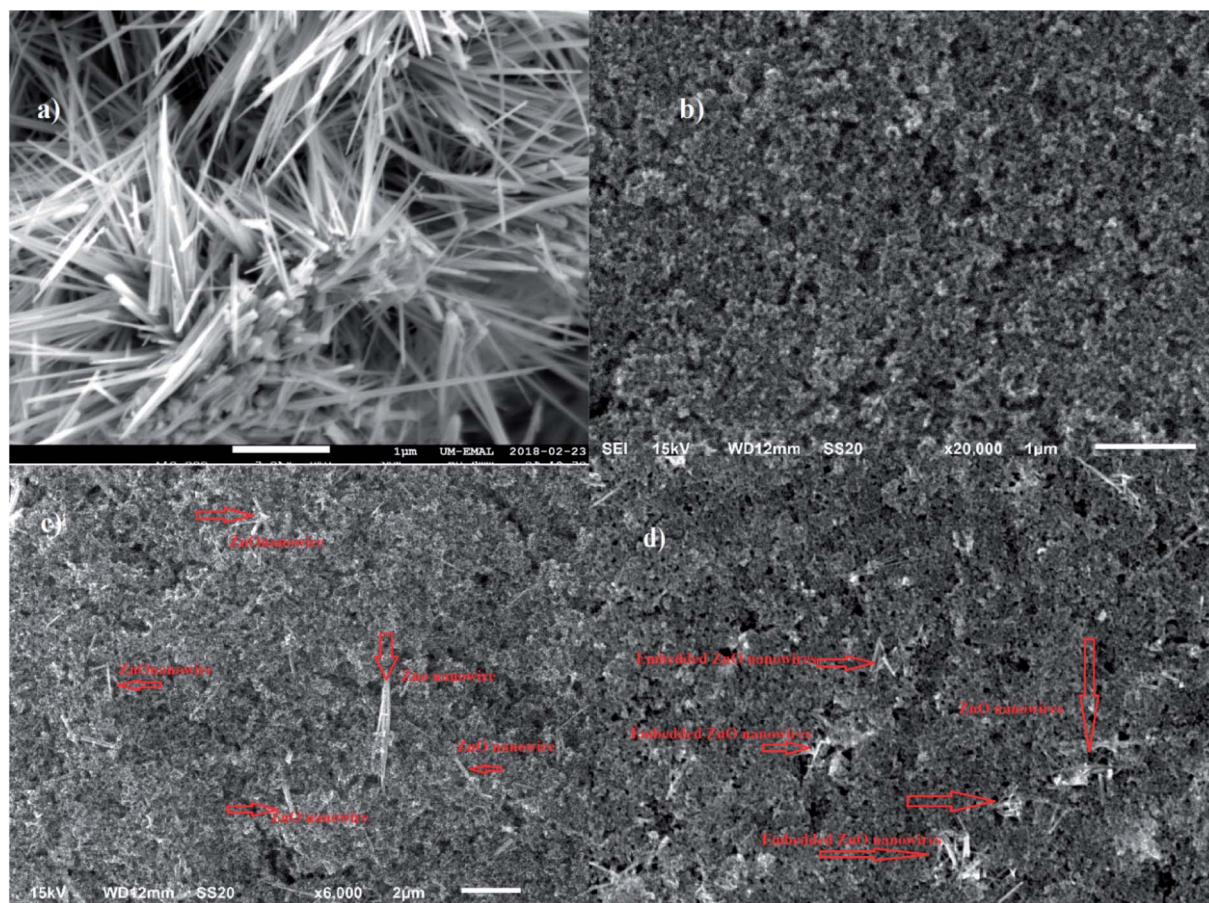


Fig. 3 (a) Pure ZnO nanowires film (b) pure TiO₂ film (c) film of TiO₂/ZnO ratio at 99 : 1 (d) film of TiO₂/ZnO ratio at 97 : 3.



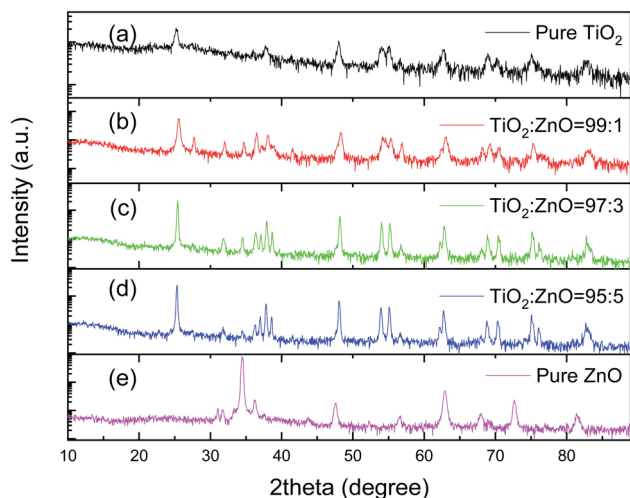


Fig. 4 XRD profiles for all electron transporting layers, (a) pure TiO_2 ; (b) $\text{TiO}_2 : \text{ZnO} = 99 : 1$; (c) $\text{TiO}_2 : \text{ZnO} = 97 : 3$; (d) $\text{TiO}_2 : \text{ZnO} = 95 : 5$; and (e) pure ZnO nanowires.

X-ray diffraction patterns in Fig. 4 corroborate that chemical composition and crystal structures of the mixtures. Fig. 4a indicates that the crystal structure of as-purchased TiO_2 is anatase, which can be identified by diffraction peaks at 2θ values of 25° , 38.1° , 48.2° , 53.9° and 55.1° , corresponding to the reflection planes of (101), (004), (200) and (105), respectively.²⁹ The XRD profile is in agreement with the standard XRD pattern (JCPDS files no. 21-1272). Fig. 4e portrays that the crystal structure of as-produced ZnO nanowires is a single hexagonal phase of wurtzite. ZnO nanowires, from hundred nanometers to micrometers in length, possess a space group of $P6_3mc$ (JCPDS card no. 36-1451) with high crystallinity. The characteristic peaks are at 31.95° , 34.6° , 36.4° , 47.7° , 56.75° , 63.0° and 68.1° , which are ascribed to the crystal planes of (100), (002), (101), (102), (110), (103), and (112), respectively. Compared with the standard diffraction patterns of ZnO, the discrepancy in the relative weak peak intensities is attributed to the fact that nanowires have preferred growth orientations. Moreover, the relative peak intensity of (100) to (002) between 31.95° and 34.6° substantiates that ZnO nanowires synthesized by various methods exhibit different preferred growth orientations. Fig. 4b–d depict XRD profiles of the mixtures, clearly illustrating that with increase in amount of the mixtures, the characteristic peaks of the ZnO, (101) at 36.4° and (103) at 63.0° become more apparent, although the peak of (101) at 36.4° of ZnO is lumped together with that of (004) at 28.1° of TiO_2 .

Photovoltaic effects of all constructed solar cells were evaluated by the photo current–voltage curves under 1 sun illumination ($\sim 100 \text{ mW cm}^{-2}$) as depicted in Fig. 5. Generally speaking, the curves of solar cells with pure TiO_2 and a ratio of 99 : 1 (in black and red, respectively) share the similar trend shape. While solar cells with pure ZnO and a ratio of 95 : 5 (in pink and blue) possess an I – V bending feature alike as portrayed in Fig. 5. Only the curve of the cell with a ratio of 97 : 3 stands alone (in green). Apparently, different electron transporting layers dramatically impact the performance of solar cells. For comparison sake, the important parameters for solar cells such as short

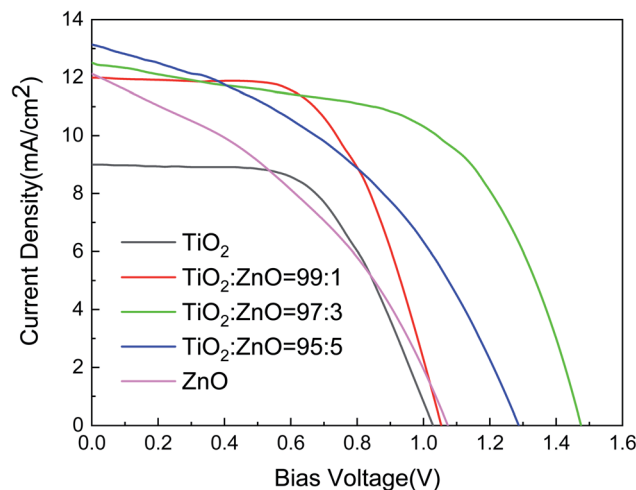


Fig. 5 The current–voltage characterization of constructed solar cells with various ETL at different ratios of TiO_2/ZnO .

circuit current density J_{sc} , open circuit voltage V_{oc} , fill factor FF, and the calculated power conversion efficiency (PCE), were summarized in Table 1. For the pure TiO_2/ZnO solar cells, the PCE reaches 4.95% and 3.95%, respectively. The TiO_2 based solar cell slightly outperforms the ZnO-based counterpart. With varying the doping amount of ZnO from a ratio of 99 : 1 to 97 : 3, the PCE increases from 7.44% to 10.53%. However, the PCE drops to 7.11%, instead of keeping on increasing above 10.53% when further increasing the doping amount of ZnO at a ratio of 95 : 5.

TiO_2 has a track record as an efficient ETL in perovskite solar cells because of its favorable energy level, easy fabrication and long electron lifetime.^{30,31} The effective mass of conduction band electrons in TiO_2 is about 5–10 m_e as compared with 0.3 m_e of ZnO, implying the available density of states is almost 2 orders of magnitude higher in TiO_2 than in ZnO, ensuring the faster and more efficient electron injection.³² On the other hand, the low electron mobility and relatively high density of electric trap states below the conduction band of TiO_2 could thwart its performance, with the PCE of 4.95% in this study. As verified by the SEM images, ZnO nanowires have a much better crystalline quality, which facilitate electron diffusion by providing a direct pathway for electron transport from the point of electron injection to the metal wire because electrons would not suffer any grain boundary scattering. Photocurrent response time in nanowires is about 2 orders of magnitude faster ($\sim 30 \mu\text{s}$), indicating that electron transport in ZnO nanowires could be improved. TiO_2 consists of small, randomly connected nanoparticles with a large number of grain

Table 1 Summarized critical parameters of solar cells

Devices	J_{sc} (mA cm^{-2})	V_{oc} (V)	FF	PCE%
TiO_2	9.04	1.03	0.532	4.95
$\text{TiO}_2 : \text{ZnO} = 99 : 1$	11.97	1.05	0.592	7.44
$\text{TiO}_2 : \text{ZnO} = 97 : 3$	12.51	1.47	0.573	10.53
$\text{TiO}_2 : \text{ZnO} = 95 : 5$	13.16	1.29	0.419	7.11
ZnO	12.18	1.07	0.303	3.95



boundaries, which act as traps/energy barriers slowing electron transport. The vast difference in the morphology of the films results in varying electron mobility. The electron mobility in ETL must be as fast as possible to efficiently extract the injected charges in order to minimize interfacial charge recombination losses. In theory, the ZnO based solar cell is expected to be better than the TiO₂ based one. However, the ETL film of relatively more compact well-connected TiO₂ nanoparticles provides more efficient pathways for electron extraction, compared with the layer of loosely netted ZnO nanowires rife with voids, which limits the microscopic electron transport and overshadows individual nanowire's faster electron transporting. It is no surprise that the ZnO based device performed poorly with a lower PCE of 3.95% in spite of better electron mobility.

With increase in the ZnO nanowire concentration from 99 : 1, 97 : 3 to 95 : 5, the PCE of the individual cells is 7.44%, 10.53% and 7.11%, respectively. The ZnO nanowires embedded TiO₂ hybrid film significantly boosted the photovoltaic performance. When two semiconductors with slightly different conduction band edges and energy positions are adopted as an electron transporting layer, an allowed fast electron transfer process paves the way for better charge separation.³³ The TiO₂ permits the formation of an energy barrier at the ZnO, because TiO₂ conduction band edge is somewhat more negative than that of ZnO. This energy barrier reduces the back electron transfer from conduction band of ZnO, thus decreasing the recombination rate and improving the cell performance. Moreover, as revealed in the SEM, the nanowires ZnO were developed into a matted film with voids. After mixing with nanoparticles TiO₂, those voids could be filled up to form relatively more compact films. A more compact electron transporting layer could result in a low series resistance, a high recombination resistance, and a low charge transfer resistance, which greatly impact the photocurrent, evidenced by better J_{sc} of cells with hybrid films at 11.97 mA cm⁻², 12.51 mA cm⁻² and 13.16 mA cm⁻², as listed in Table 1. Furthermore, the electron diffusion coefficient of ZnO nanowires is several hundred times higher than that of TiO₂ nanoparticles.³⁴ Due to the high crystal

quality and collateral dimension, the introduction of ZnO nanowires reduces the number of grain boundaries and provides straight pathways for generated electrons to effortlessly pass through, instead of zigzagging through nanoparticles with numerous barriers leading to high possibility of recombination. Additionally, ZnO nanowires with lengths in the range of hundreds of nanometers to micrometers can serve as light scattering centers to enhance the light harvest efficiency. As a result, the better performance of solar cells with hybrid films can be attributed to the synergetic effect of both TiO₂/ZnO constituent properties as electron transporting layers.

The PCE of the device with a hybrid film at a ratio of 97 : 3 reaches 10.53%, outperforming the one with 7.11% at a ratio of 95 : 5, suggesting that the higher concentration of ZnO nanowires does not ensure the better photovoltaic performance. A larger amount of ZnO nanowires in ETL could shift the conduction band of electrode, which impedes the charge separation and efficient transporting to the semiconductor electrode, thus being detrimental in photovoltaic performance.³⁵ Therefore, it could be reasonably argued that an appropriate amount of ZnO nanowires embedded in TiO₂ films could optimize the ETL property by improving charge separation, charge transporting and light harvesting, consequently, elevating the overall photovoltaic performance.

Different possible factors can affect the ideality values (the curve shape) such as: series resistance, shunt resistance, temperature, carriers' mobility, tunneling, generation-recombination, interface impurity, interfacial oxide layer and so on. Some localized defect states of TiO₂/ZnO may lie in semiconductors' forbidden gap. The semiconductor localized states can act as carrier trapping centers. Carriers from electrodes trapped in these centers and these localized states become charged. Subsequently, a space charge region would be built up, which has a strong effect on the J - V characteristics of a device, especially at higher bias levels because the trapped carriers contribute to the conduction paths. The unique J - V characteristics of the cell with a ratio of 97 : 3 results from the presence of the built-up charged region, which minimizes the

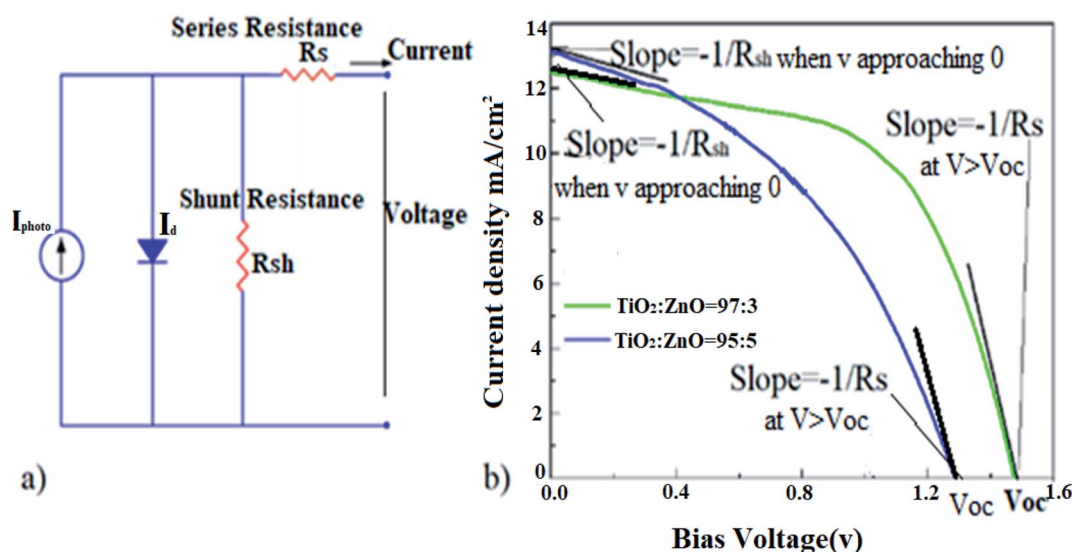


Fig. 6 (a) Diagrammatic sketch of the equivalent circuit of a solar cell (b) estimated R -shunt and R -series.



energy loss, leading to the highest V_{oc} of 1.47 V. By ruling out the other factors, the non-ideality in a solar cell is largely associated with the shunt resistance (R_{sh}) and the series resistance (R_s) as depicted in Fig. 6a. The series resistance and shunt resistance can be calculated by $-dV/dJ$ based on the diode equation for each cell.³⁶ Roughly speaking, solar cells with pure TiO_2 and a ratio of 99 : 1 (in black and red, respectively) share the comparable R_{sh} and R_s , leading to the curve shape alike. While R_{sh} and R_s in solar cells based on pure ZnO and a mixture with a ratio of 95 : 5 are close enough to share the similar $-dV/dJ$ at V approaching to 0 and $V > V_{oc}$ as illuminated in Fig. 6b.

Due to the increased effective tolerance factor, $CsPbI_2Br$ has demonstrated enhanced phase stability when exposed to moisture in ambient conditions, compared with other all inorganic Cs-based perovskites.³⁷ Since being first developed, the PCE of $CsPbI_2Br$ based solar cells has been reported to achieve 16.37% within 2 years,³⁸ which holds great potential for breakthroughs in the solar energy field. Certainly, a substantial amount of research to ameliorate all components of n-i-p solar cells is still needed to bridge the gap between today's benchmark conversion efficiency and the predicted 32% by the Shockley-Queisser limit of a single junction cell. At present, no material/configuration of devices has been identified as the best option to optimize the overall performance of perovskite solar cells. The obtained insights in this work could provide some rationales on design of better performing perovskite solar devices, a step forward in realization of practical applications, which could pave the way for further improvement, and accelerate more breakthroughs in perovskite solar cells for eventual commercialization.

Conclusions

The relatively more stable all-inorganic $CsPbI_2Br$ has been attempted as a light absorber, along with various electron transporting films to construct solar cells. The comparative study was conducted to look into the photovoltaic performance for all solar devices. It turns out that solar cells with ZnO nanowires embedded TiO_2 as an electrode outperformed those with pure TiO_2 or pure ZnO. The enhanced performance is attributed to the synergetic effect of both TiO_2 /ZnO constituent properties. TiO_2 nanoparticles with the longer electron life time/higher density of states, in conjunction with ZnO nanowires with the better electron mobility/light harvesting, formed a compact electron selective layer with lower charge transfer resistance, leading to the better power conversion efficiency. In particular, an appropriate amount of ZnO nanowires embedded in TiO_2 films could optimize the property electron transport layer by improving charge separation, charge transporting and light harvesting, as a result, the highest power conversion efficiency of 10.53% among them can be achieved.

Conflicts of interest

Authors declare there is no conflict of interest.

Acknowledgements

This work was supported by National Science Foundation (NSF) (Grant No. 1700339).

References

- 1 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, Organometal Halide Perovskites as Visible-Light Sensitizers for photovoltaic Cells, *J. Am. Chem. Soc.*, 2009, **131**, 6050.
- 2 H. S. Jung and N. G. Park, Perovskite Solar Cells: From Materials to Devices, *Small*, 2015, **11**, 10.
- 3 NREL efficiency chart, <https://www.nrel.gov/pv/assets/images/efficiency-chart.png>.
- 4 K. Domanski, J. Correa-Baena, N. Mine, M. Nazeeruddin, A. Abate, M. Saliba, W. Tress, A. Hagfeldt and M. Grätzel, Not All That Glitters Is Gold: Metal-Migration-Induced Degradation in Perovskite Solar Cells, *ACS Nano*, 2016, **10**, 6306.
- 5 J. Y. Guan, J. Ni, X. J. Zhou, Y. Liu, J. Y. Yin, J. L. Wang, D. Wang, Y. F. Zhang, J. Li, H. K. Cai and J. J. Zhang, High-Performance Electron Transport Layer *via* Ultrasonic Spray Deposition for Commercialized Perovskite Solar Cells, *ACS Appl. Energy Mater.*, 2020, **3**(12), 11570–11580.
- 6 E. Sundin, R. Ringström, F. Johansson, B. Kücküköz, A. Ekebergh, V. Gray, B. Albinsson, J. Mårtensson and M. Abrahamsson, Singlet Fission and Electron Injection from the Triplet Excited State in Diphenylisobenzofuran–Semiconductor Assemblies: Effects of Solvent Polarity and Driving Force, *J. Phys. Chem. C*, 2020, **124**(38), 20794–20805, DOI: 10.1021/acs.jpcc.0c06626.
- 7 J. A. Smith, O. S. Game, J. E. Bishop, E. L. K. Spooner, R. C. Kilbride, C. Greenland, R. Jayaprakash, T. I. Alanazi, E. J. Cassella, A. Tejada, G. Chistiakova, M. I. Wong-Stringer, T. J. Routledge, A. J. Parnell, D. B. Hammond and D. G. Lidzey, Rapid Scalable Processing of Tin Oxide Transport Layers for Perovskite Solar Cells, *ACS Appl. Energy Mater.*, 2020, **3**(6), 5552–5562, DOI: 10.1021/acsaem.0c00525.
- 8 R. Jose, V. Thavasi and S. Ramakrishna, Metal Oxides for Dye-Sensitized Solar Cells, *J. Am. Ceram. Soc.*, 2009, **92**, 289.
- 9 D. Q. Bi, G. Boschloo, S. Schwarzmueller, L. Yang, E. M. Johansson and A. Hagfeldt, Efficient and stable $CH_3NH_3PbI_3$ -sensitized ZnO nanorod array solid state solar cells, *Nanoscale*, 2012, **5**, 11686.
- 10 D. Y. Son, J.-H. Im, H. S. Kim and N.-G. Park, 11% Efficient Perovskite Solar Cell Based on ZnO Nanorods: An Effective Charge Collection System, *J. Phys. Chem. C*, 2014, **118**, 16567–16573.
- 11 J. J. Shi, X. Xu, D. M. Li and Q. B. Meng, Interfaces in Perovskite Solar Cells, *Small*, 2015, **11**(No. 21), 2472–2486.
- 12 P. Tiwana, P. Docampo, M. B. Johnston, H. J. Snaith and L. M. Herz, Electron Mobility and Injection Dynamics in Mesoporous ZnO, SnO_2 , and TiO_2 Films Used in Dye-Sensitized Solar Cells, *ACS Nano*, 2011, 5158–5166.
- 13 Y. Q. Wang, Y. M. Sun and K. Li, Dye-sensitized solar cell based on oriented ZnO nanowire-covered TiO_2 nanoparticle composite film electrodes, *Mater. Lett.*, 2002, **63**, 1102–1104.
- 14 Y. Bai, H. Yu, Z. Li, R. Amal, G. Q. Liu and L. Z. Wang, *In Situ* Growth of a ZnO nanowire network within a TiO_2



- nanoparticle film for enhanced dye-sensitized solar cell performance, *Adv. Mater.*, 2012, **24**, 5850–5856.
- 15 W. P. Hu, S. F. Yang and S. H. Yang, Surface Modification of TiO₂ for Perovskite Solar Cells, *Trends Chem.*, 2020, 148–162.
 - 16 J. Luo, Y. X. Wang and Q. F. Zhang, Progress in perovskite solar cells based on ZnO nanostructures, *J. Sol. Energy*, 2018, 289–306.
 - 17 Z. P. Hu, Z. Z. Liu, Y. Bian, D. J. Liu, X. S. Tang, W. Hu, Z. G. Zang, M. Zhou, L. D. Sun, J. X. Tang, Y. Q. Li, J. Du and Y. X. Leng, Robust Cesium Lead Halide Perovskite Microcubes for Frequency Upconversion Lasing, *Adv. Opt. Mater.*, 2017, **5**, 1700419, DOI: 10.1002/adom.201700419.
 - 18 J. Z. Song, J. H. Li, X. M. Li, L. M. Xu, Y. H. Dong and H. B. Zeng, Quantum Dot Light-Emitting Diodes Based on Inorganic Perovskite Cesium Lead Halides, *Adv. Mater.*, 2015, **27**, 7162–7167, DOI: 10.1002/adma.201502567.
 - 19 Y. Li, Z.-F. Shi, S. Li, L.-Z. Lei, H.-F. Ji, D. Wu, T.-T. Xu, Y.-T. Tian and X.-J. Li, High-performance perovskite photodetectors based on solution-processed all-inorganic CsPbBr₃ thin films, *J. Mater. Chem. C*, 2017, **5**, 8355–8360, DOI: 10.1039/c7tc02137b.
 - 20 G. E. Eperon, G. M. Paterno, R. J. Sutton, A. Zampetti, A. A. Haghighirad, F. Cacialli and H. J. Snaith, Inorganic caesium lead iodide perovskite solar cells, *J. Mater. Chem. A*, 2015, **3**, 19688–19695.
 - 21 L. Yan, Q. Xue, M. Liu, Z. Zhu, J. Tian, Z. Li, Z. Chen, Z. Chen, H. Yan, H.-L. Yip and Y. Cao, Interface Engineering for All-Inorganic CsPbI₂Br Perovskite Solar Cells with Efficiency over 14%, *Adv. Mater.*, 2018, **30**, 1802509.
 - 22 Y. Guo, X. Yin, J. Liu and W. Que, Highly efficient CsPbI₂Br perovskite solar cells with efficiency over 9.8% fabricated using a preheating-assisted spin-coating method, *J. Mater. Chem. A*, 2019, **7**, 1900.
 - 23 C.-C. Lin and Y.-Y. Li, Synthesis of ZnO nanowires by thermal decomposition of zinc acetate dihydrate, *Mater. Chem. Phys.*, 2009, **113**, 334–337.
 - 24 S. Zhang, S. Wu, W. Chen, H. Zhu, Z. Xiong, Z. Yang, C. Chen, R. Chen, L. Han and W. Chen, Solvent engineering for efficient inverted perovskite solar cells based on inorganic CsPbI₂Br light absorber, *Mater. Today Energy*, 2018, **8**, 125.
 - 25 Y. L. Z. F. Shi, S. Li, L. Z. Lei, H. F. Ji, D. Wu, T. T. Xu, Y. T. Tian and X. J. Li, High performance perovskite photodetectors based on solution-processed all-inorganic CsPbX₃ thin films, *J. Mater. Chem. C*, 2017, **5**, 8355–8360, DOI: 10.1039/C7TC02137B.
 - 26 C. C. Stoumpos and M. G. Kantzidis, The renaissance of halide perovskites and their evolution as emerging semiconductors, *Acc. Chem. Res.*, 2015, **48**(10), 2791–2802.
 - 27 K. Ubaid, Z. N. Yu, A. K. Abbas, Z. Almas and U. Naeem, High performance CsPbI₂Br perovskite solar cells with Zinc and Manganese doping, *Nanoscale Res. Lett.*, 2019, **14**, 116.
 - 28 J. G. Zhang, Z. W. Jin, L. Liang, H. R. Wang, D. L. Bai, H. Bian, K. Wang, Q. Wang, N. Y. Yuan, J. N. Ding and S. Z. Liu, Iodine-Optimized Interface for Inorganic CsPbI₂Br Perovskite Solar Cell to Attain High Stabilized Efficiency Exceeding 14%, *Adv. Sci.*, 2018, **5**, 1801123.
 - 29 A. J. Haider, R. H. Al-Anbari, G. R. Kadhim and C. T. Salame, Exploring potential environmental applications of TiO₂ nanoparticles, *Energy Procedia*, 2017, **119**, 332–345.
 - 30 M. Liu, M. B. Johnston and H. J. Snaith, Efficient planar heterojunction perovskite solar cells by vapor deposition, *Nature*, 2013, **501**, 395.
 - 31 J. Burschka, N. Pellet, S.-J. Moon, R. Humphry-Baker, P. Gao, M. K. Nazeeruddin and M. Grätzel, Sequential deposition as a route to high-performance perovskite-sensitized solar cells, *Nature*, 2013, **499**, 316.
 - 32 N. A. Anderson, X. Ai and T. Q. Lian, Electron injection dynamics for Ru Polypyridyl complexes to ZnO nanocrystalline thin films, *J. Phys. Chem. B*, 2003, **107**, 14414–14421.
 - 33 C. K. Xu, J. M. Wu, U. V. Desai and D. Gao, High efficiency solid state dye-sensitized solar celled based on TiO₂ coated ZnO nanowire arrays, *Nano Lett.*, 2012, **12**, 2420–2424.
 - 34 M. Law, L. E. Greene, J. C. Johnson, R. Saykally and P. Yang, Nanowire dye-sensitized solar, *Nat. Mater.*, 2005, **4**, 455.
 - 35 S. Pang, T. F. Xie, Y. Zhang, X. Wei, M. Yang, D. J. Wang and Z. L. Du, Research on the Effect of Different Sizes of ZnO Nanorods on the Efficiency of TiO₂-Based Dye-Sensitized Solar Cells, *J. Phys. Chem. C*, 2007, **111**, 18417.
 - 36 W. J. Ke, G. J. Fang, J. Wang, P. L. Qin, H. Tao, H. W. Lei, Q. Liu, X. Dai and X. Z. Zhao, Perovskite Solar Cell with an Efficient TiO₂ Compact Film, *ACS Appl. Mater. Interfaces*, 2014, **6**, 15959–15965.
 - 37 Q. S. Zeng, X. Y. Zhang, C. M. Liu, T. L. Feng, Z. L. Chen, W. Zhang, W. T. Zheng, H. Zhang and B. Yang, Inorganic CsPbI₂Br Perovskite solar cells: the progress and perspective, *Advanced Science, Sol. RRL*, 2019, **3**, 1800239.
 - 38 Y. Q. Zhang, C. C. Wu, D. Wang, Z. H. Zhang, X. Qi, N. Zhu, G. H. Liu, X. D. Li, H. Z. Hu, Z. J. Chen, L. X. Xiao and B. Qu, High Efficiency (16.37%) of Cesium Bromide—Passivated All-Inorganic CsPbI₂Br Perovskite Solar Cells, *Sol. RRL*, 2019, **3**, 1900254.

