

## PAPER

View Article Online  
View Journal | View Issue

# Tuning the degree of CO<sub>2</sub> activation by carbon doping Cu<sub>n</sub><sup>−</sup> (*n* = 3–10) clusters: an IR spectroscopic study†

 Olga V. Lushchikova,<sup>ab</sup> Máté Szalay,<sup>d</sup> Tibor Höltzl<sup>cd</sup>  
and Joost M. Bakker<sup>id</sup>\*<sup>a</sup>

Received 16th June 2022, Accepted 19th August 2022

DOI: 10.1039/d2fd00128d

Copper clusters on carbide surfaces have shown a high catalytic activity towards methanol formation. To understand the interaction between CO<sub>2</sub> and the catalytically active sites during this process and the role that carbon atoms could play in this, they are modeled by copper clusters, with carbon atoms incorporated. The formed clusters Cu<sub>n</sub>C<sub>m</sub><sup>−</sup> (*n* = 3–10, *m* = 1–2) are reacted with CO<sub>2</sub> and investigated by IR multiple-photon dissociation (IR-MPD) spectroscopy to probe the degree of CO<sub>2</sub> activation. IR spectra for the reaction products [Cu<sub>n</sub>C·CO<sub>2</sub>]<sup>−</sup>, (*n* = 6–10), and [Cu<sub>n</sub>C<sub>2</sub>·CO<sub>2</sub>]<sup>−</sup>, (*n* = 3–8) are compared to reference spectra recorded for products formed when reacting the same cluster sizes with CO, and with density functional theory (DFT) calculated spectra. The results reveal a size- and carbon load-dependent activation and dissociation of CO<sub>2</sub>. The complexes [Cu<sub>n</sub>C·CO<sub>2</sub>]<sup>−</sup> with *n* = 6 and 10 show predominantly molecular activation of CO<sub>2</sub>, while those with *n* = 7–9 show only dissociative adsorption. The addition of the second carbon to the cluster leads to the exclusive molecular activation of the CO<sub>2</sub> on all measured cluster sizes, except for Cu<sub>5</sub>C<sub>2</sub><sup>−</sup> where CO<sub>2</sub> dissociates. Combining these findings with DFT calculations leads us to speculate that at lower carbon-to-metal ratios (CMRs), the C can act as an oxygen anchor facilitating the OC=O bond rupture, whereas at higher CMRs the carbon atoms increasingly attract negative charge, reducing the Cu cluster's ability to donate electron density to CO<sub>2</sub>, and consequently its ability to activate CO<sub>2</sub>.

<sup>a</sup>Radboud University, Institute for Molecules and Materials, FELIX Laboratory, Toernooiveld 7, 6525 ED Nijmegen, The Netherlands. E-mail: joost.bakker@ru.nl

<sup>b</sup>Institut für Ionenphysik und Angewandte Physik, Universität Innsbruck, Technikerstraße 25, 6020 Innsbruck, Austria

<sup>c</sup>MTA-BME Computation Driven Chemistry Research Group, Department of Inorganic and Analytical Chemistry, Budapest University of Technology and Economics, Muegyetem rkp. 3, Budapest 1111, Hungary

<sup>d</sup>Furukawa Electric Institute of Technology, Késmárk Utca 28/A, 1158 Budapest, Hungary

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2fd00128d>



# Introduction

The continuous growth of carbon emissions has led, and continues to lead, to an accumulation of CO<sub>2</sub> in the atmosphere, and the concomitant global warming. To mitigate this, an urgent solution is needed to reduce atmospheric CO<sub>2</sub> concentrations. At the same time, CO<sub>2</sub> is the largest carbon source on Earth, and it could be used as a feedstock for many valuable chemicals, such as alcohols and other higher hydrocarbons. The bottleneck lies in the high kinetic and thermal stability of the CO<sub>2</sub> molecule, expressed in the C=O bond energy of more than 7 eV.<sup>1</sup>

One promising way for CO<sub>2</sub> utilization is its hydrogenation to simple alcohols like methanol. Industrially this process takes place over a Cu/ZnO/Al<sub>2</sub>O<sub>3</sub> catalyst at temperatures of 200–300 °C and pressures of 50–100 bar.<sup>2</sup> The energy required to drive this reaction leads to additional CO<sub>2</sub> emissions and elevated costs, while the one-pass selectivity towards methanol formation is rather low, with larger concentrations of CO and H<sub>2</sub>O formed. Thus, for direct CO<sub>2</sub> conversion, a more selective catalyst is required. Many different catalyst materials have been tested to reduce reaction temperatures and increase the methanol yield.

One issue that seems not to affect relatively well-functioning CO<sub>2</sub> hydrogenation catalysts is poisoning due to coke formation, a process that hampers the reverse reaction during methanol decomposition.<sup>3</sup> Rather, metal carbide catalyst materials have shown enhanced activity in CO<sub>2</sub> activation. This enhancement has been rationalized by increased catalyst stability upon adding carbon to the metal, and by the modification of the metal's electronic and structural properties, changing its catalytic activity.<sup>4,5</sup> Transition metal carbides (TMCs) have even demonstrated chemical activity similar, and sometimes even better, than that of the platinum group metals in the transformation of hydrocarbons and oxygen-containing molecules.<sup>6–8</sup> TMCs are also considered to be promising catalysts for CO<sub>2</sub> conversion by H<sub>2</sub>.<sup>8</sup> However, experimentally, it was shown that, for example, Mo<sub>2</sub>C is quite aggressive and leads to CO<sub>2</sub> dissociation, forming CO and H<sub>2</sub>O, *via* the reverse water gas shift (rWGS) reaction.<sup>9,10</sup> Based on density functional theory (DFT) calculations, it is suggested that Mo<sub>8</sub>C<sub>12</sub> nanoparticles are better catalysts, considering their high stability and moderate chemical activity in comparison to that of bulk Mo (too low) and Mo<sub>2</sub>C (too high).<sup>11</sup> Similar conclusions were drawn for Ti carbides.<sup>11</sup> Some transition metal catalysts with a carbon-to-metal ratio (CMR) below 1 easily break the C–O bond leading to CO formation.<sup>6,7</sup> An increase in carbon content may enhance catalyst stability, it also leads to a decrease of the chemical activity, for instance observed for TiC and MoC, due to the ligand effect expressed in a downshift of the metal d-band center affecting the charge transfer from the metal to CO<sub>2</sub> and, thus, also adsorption energy.<sup>7,11–13</sup> Accordingly, the activity of a metal carbide catalyst towards CO<sub>2</sub> dissociation can be tuned by varying the CMR of the catalyst.<sup>14</sup>

TMC catalytic activity can also be altered by the deposition of other metals on the TMC surface.<sup>5,7,10,14</sup> Cu-promoted carbides exhibit enhanced selectivity towards methanol formation in comparison to both bare copper and bare TMC surfaces, like TaC, SiC, TiC, Mo<sub>2</sub>C, and MoC.<sup>5,7,14</sup> It is also pointed out that the Cu–TMCs interface plays a crucial role. The hydrogenation of the reaction intermediates, such as HCO and H<sub>2</sub>CO, is energetically more favorable on the Cu sites, making small Cu clusters more suitable catalysts for methanol formation.<sup>5,14</sup> Cu<sub>4</sub>/



TiC has an even higher CO<sub>2</sub> adsorption energy, and therefore methanol formation rate, than the commercial Cu/ZnO catalyst.<sup>5,15,16</sup> However, most Cu/TMC catalyzed reactions proceed *via* CO formation and its subsequent hydrogenation, rather than *via* direct CO<sub>2</sub> hydrogenation and a formate intermediate, as is the widely accepted reaction pathway over Cu catalysts.<sup>2</sup> The high selectivity towards CO results in an elevated CO yield at the expense of methanol production. Therefore, it is important to understand what the direct influence of carbon is on the deposited clusters and how it influences CO<sub>2</sub> activation.

The fine details of a reaction proceeding on the active sites can be studied at the molecular level using isolated clusters. Mass-selective gas-phase spectroscopy allows studying the interaction of CO<sub>2</sub> with clusters of well-defined elemental composition. For example, photoelectron and IR spectroscopy have been used to study the interaction between CO<sub>2</sub> and metal anions.<sup>17–27</sup> This interaction can be characterized by four binding motifs: bidentate ( $\eta^2$ ), metal formate, oxalate, and dissociative adsorption. The variety in CO<sub>2</sub> adsorption motifs is related to the difference in the degree of electron transfer from the metal center into the anti-bonding  $2\pi_u$  LUMO of CO<sub>2</sub>.<sup>28</sup> For Cu<sup>−</sup> and other coinage metal ions in particular, it was found that CO<sub>2</sub> binds in a formate-like fashion, where the metal ion replaces the hydrogen.<sup>17,19</sup> The reaction of CO<sub>2</sub> with isolated anionic metal clusters was also studied with flow tube reactor mass spectrometry,<sup>29,30</sup> and IR spectroscopy.<sup>31,32</sup> The nature of CO<sub>2</sub> adsorption on these clusters appears to be size-dependent, for example on Pt<sub>*n*</sub><sup>−</sup> clusters, where Pt<sub>4</sub><sup>−</sup> shows CO<sub>2</sub> activation, whereas Pt<sub>5</sub><sup>−</sup>, Pt<sub>6</sub><sup>−</sup> and Pt<sub>7</sub><sup>−</sup> show dissociation.<sup>31</sup> Another example is Co<sub>*n*</sub><sup>−</sup>, where the Co<sup>−</sup> ion binds two CO<sub>2</sub> molecules in a bidentate configuration,<sup>27</sup> and clusters with *n* > 7 dissociate CO<sub>2</sub>.<sup>32</sup>

In this work, we investigate how the carbon doping of anionic Cu clusters will influence the degree of CO<sub>2</sub> activation, where the anionic charge state was chosen to facilitate electron transfer to the CO<sub>2</sub> molecule. Anionic copper clusters containing 5–10 Cu atoms were doped with one or two C atoms and reacted with CO<sub>2</sub>. The formed [Cu<sub>*n*</sub>C<sub>*m*</sub>·CO<sub>2</sub>]<sup>−</sup> species, with *n* = 3–10 and *m* = 1–2, were studied by mass-selective IR spectroscopy. The obtained spectra are compared to reference IR spectra of the clusters reacted with CO and with DFT calculated spectra.

## Methods

The experiment is shown schematically in Fig. 1. Carbon-doped anionic copper clusters Cu<sub>*n*</sub>C<sub>*m*</sub><sup>−</sup> are produced in a Smalley-type laser ablation source.<sup>33</sup> An isotopically enriched Cu-65 (99.9%) target is ablated by the focused second harmonic of a Nd:YAG laser (532 nm, 14 mJ) in the presence of a He carrier gas that is injected by a pulsed valve (General Valve series 9, stagnation pressure 6 bar). Carbon-doped copper clusters were formed due to the presence of trace carbon in the carrier gas or residual pump oil vapour. The formed clusters are reacted with CO<sub>2</sub> or CO by injecting the pure gases through a second pulsed valve with a 1 bar stagnation pressure into an extension of the clustering channel. The Cu<sub>*n*</sub>C<sub>*m*</sub><sup>−</sup> clusters react with CO<sub>2</sub> or CO at room temperature in a reaction channel, forming [Cu<sub>*n*</sub>C<sub>*m*</sub>·CO<sub>2</sub>]<sup>−</sup> or [Cu<sub>*n*</sub>C<sub>*m*</sub>·CO]<sup>−</sup> complexes with *n* = 3–10, and *m* = 1–2. The bracket notation implies that no prior knowledge of the adsorption form of CO or CO<sub>2</sub> is assumed. The gas mixture of helium and clusters is expanded into vacuum, forming a molecular beam that is collimated



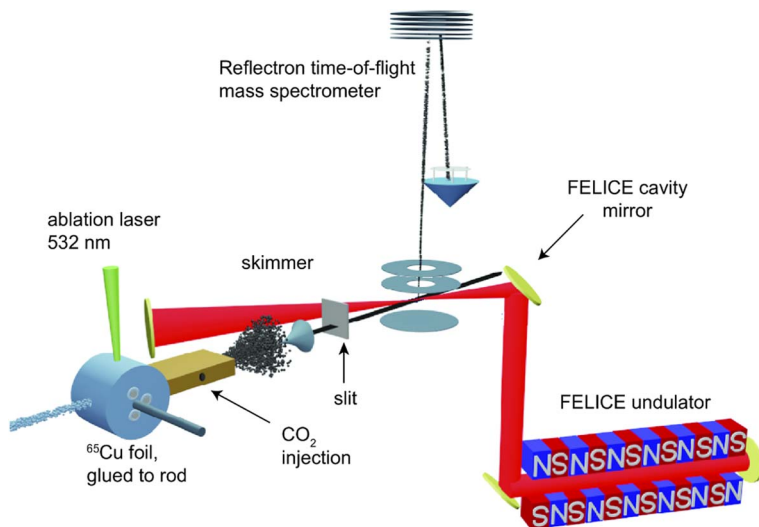


Fig. 1 Schematic of experimental setup.

by a 2 mm diameter skimmer and an  $8 \times 2$  mm slit aperture. The ions are then irradiated by IR laser light, and subsequently pulse-extracted by high voltage plates into an orthogonal time-of-flight mass spectrometer (TOF-MS), where they are mass separated and detected by a multichannel plate (MCP) detector. For the spectroscopic experiments, the molecular beam overlaps between the extraction plates at a  $35^\circ$  angle with the IR laser beam of the free-electron laser for intracavity experiments (FELICE).<sup>34</sup> IR light is produced in the form of macropulses, consisting of an approximately 10  $\mu$ s pulse train of transform-limited ps duration micropulses, and is characterized by a spectral bandwidth of  $\sim 0.7\%$  of the central frequency. The frequency range covered in this work is  $320\text{--}2120\text{ cm}^{-1}$ , with typical macropulse energies of  $0.06\text{--}0.8\text{ J}$ , and fluences of  $0.7\text{--}6.1\text{ J cm}^{-2}$ . The experiment is operated at twice the IR laser frequency, and mass spectra with and without irradiation are recorded to correct for the fluctuations during cluster production. IRMPD spectra are obtained by calculating the depletion yield  $Y(\nu)$  at frequency  $\nu$ , defined as:

$$Y(\nu) = -\ln\left(\frac{I_{\text{on}}(\nu)}{I_{\text{off}}}\right) / P,$$

where  $I_{\text{on}}(\nu)$  is the ion intensity of the irradiated complex,  $I_{\text{off}}$  the ion intensity without irradiation, and  $P$  the macropulse energy. Spectra displaying the depletion  $I_{\text{on}}(\nu)/I_{\text{off}}$  can be found in Fig. S1† of the ESI.

For the structural assignment of selected spectra (for  $\text{Cu}_6\text{C}^-$  and  $\text{Cu}_7\text{C}^-$ ), DFT calculations of different isomers were done using the Q-Chem 5.3 program package.<sup>35</sup> Stable structures were identified using the TPSSH/def2-TZVP + D3 level of theory,<sup>36</sup> as described in the ESI.† A detailed description of the search procedure is given in the ESI.† This combination of functional, basis set and dispersion correction was chosen to be able to directly compare the results with our previous work on the adsorption of  $\text{CO}_2$  on cationic Cu clusters,<sup>37</sup> where adsorption was



limited to physisorption. The accuracy of this method was carefully evaluated compared to a CCSD(T)/def2-QZVPPD benchmark.<sup>37</sup> In other studies it has been found that the precise mode of physisorption found in these calculations can markedly be influenced by the choice of dispersion correction.<sup>38</sup> However, since the interaction for the species under study here is significantly stronger, as seen by the activated and dissociated products discussed below, we believe that these influences are not decisive here. This is confirmed by further DFT based computations with D3 or D4 and without dispersion correction (Table S1 in the ESI†).

Only the lowest spin multiplicities were considered in the calculations, so doublet for  $\text{Cu}_6\text{C}^-$ , and singlet for  $\text{Cu}_7\text{C}^-$ . Harmonic vibrational frequencies of these structures are convoluted with  $20\text{ cm}^{-1}$  Gaussian line shape function and compared to the experimental data for final assignment. No frequency scaling has been applied for the comparison.

## Results and discussion

To understand how  $\text{CO}_2$  binds to anionic carbon-doped copper clusters, IRMPD spectra of products formed upon reacting  $\text{Cu}_n\text{C}_m^-$  ( $n = 3-10$ ) with different carbon loading  $m = 1-2$  are recorded. A mass spectrum of all species formed is shown in Fig. 2. From this figure, one can see that for each size  $n$ , a distribution of  $\text{Cu}_n\text{C}_m^-$  clusters is formed, that for larger clusters ( $n \geq 9$ ) is essentially limited to  $m = 0-3$ . Pure  $\text{Cu}_n^-$  clusters are lower in intensity than the carbon doped clusters, which we attribute to a more facile formation of a  $\text{CuC}^-$  seed as a nucleation core than  $\text{Cu}_2^-$ .

In the inset, a close-up of the mass spectrum in the region close to  $\text{Cu}_6^-$  and  $\text{Cu}_7^-$  is shown, with individual mass peaks corresponding to  $\text{Cu}_n\text{C}_m(\text{CO}_2)_p^-$  labeled by ( $n$  and  $m$ ) or ( $n$ ,  $m$  and  $p$ ). It can be seen that the pure Cu

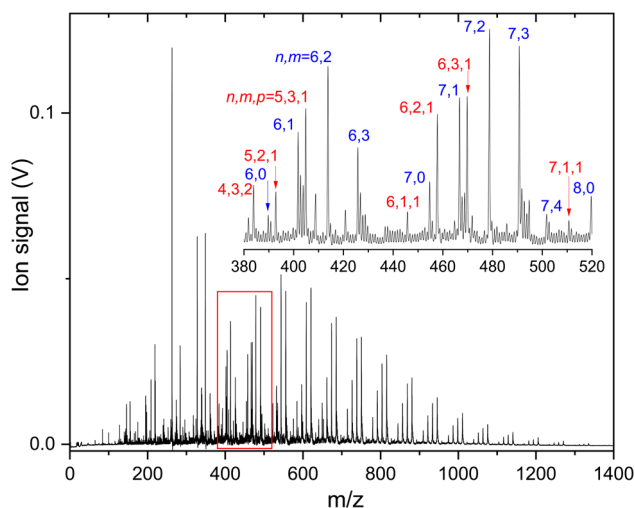


Fig. 2 Mass spectrum of the products formed when reacting anionic  $\text{Cu}_n\text{C}_m^-$  clusters with  $\text{CO}_2$ . Mass peaks in the inset are labeled by ( $n$  and  $m$ ) or ( $n$ ,  $m$ , and  $p$ ) for  $\text{Cu}_n\text{C}_m(\text{CO}_2)_p^-$ .



clusters are produced in this mass spectral region too, albeit at lower intensity than the  $\text{Cu}_n\text{C}^-$ ,  $\text{Cu}_n\text{C}_2^-$ , and  $\text{Cu}_n\text{C}_3^-$  signals. Unfortunately,  $\text{CO}_2$  adsorption on the pure  $\text{Cu}_n^-$  clusters is negligible, precluding spectroscopic characterization.

### $\text{CO}_2$ activation by $\text{Cu}_n\text{C}^-$

The IRMPD spectra of low-carbon loading products  $[\text{Cu}_n\text{C}\cdot\text{CO}_2]^-$  ( $n = 6-10$ ) are shown in Fig. 3 (panels a–e). The complexes with  $n = 7-9$  show only one main band around  $2000\text{ cm}^{-1}$ , which is fairly close to the frequency of the free C–O stretch vibration at  $2143\text{ cm}^{-1}$ .<sup>39</sup> We can thus speculate that these cluster sizes adsorb  $\text{CO}_2$  dissociatively, leading to the formation of CO. In contrast, the spectra of complexes with  $n = 6$  and 10 are dominated by two bands around  $720$  and  $1630\text{ cm}^{-1}$ , with a weaker band visible around  $1100\text{ cm}^{-1}$ . Earlier, experimental IR studies of the  $\text{CO}_2^-$  radical embedded in alkali halide matrices have revealed a characteristic band at  $1671\text{ cm}^{-1}$ .<sup>40</sup> The presence of a band in this region in the IRMPD spectra suggests that  $\text{Cu}_n\text{C}^-$  clusters with  $n = 6$  and 10 induce a distortion

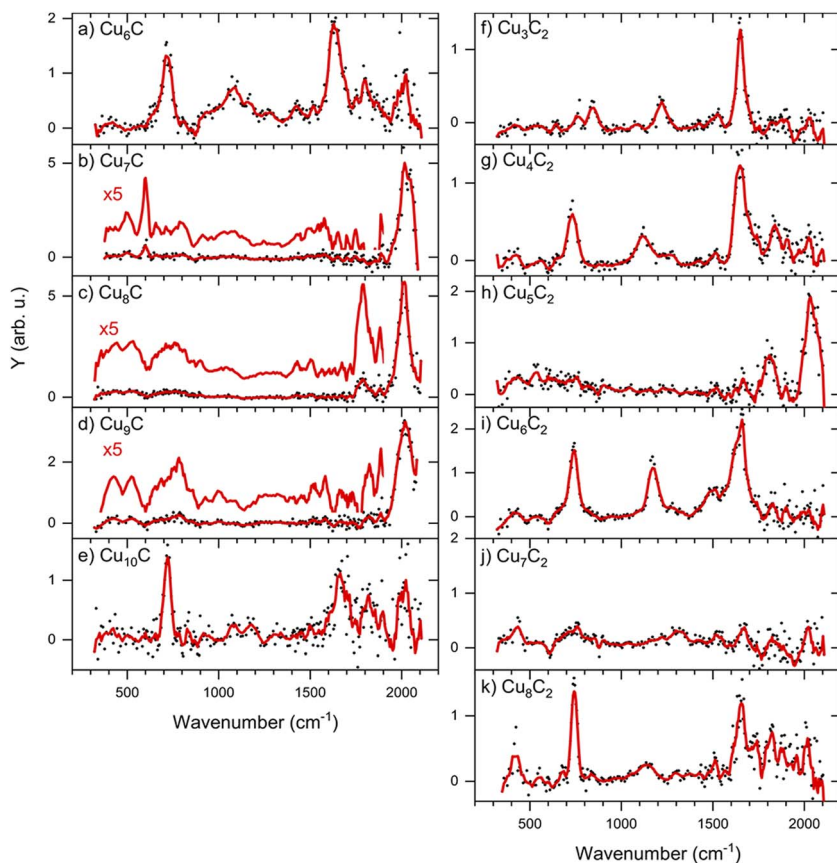


Fig. 3 IRMPD spectra of  $[\text{Cu}_n\text{C}\cdot\text{CO}_2]^-$  (left) and  $[\text{Cu}_n\text{C}_2\cdot\text{CO}_2]^-$  (right). The red lines are five-point adjacent-averages of the solid dots.



of CO<sub>2</sub>, activating it. Bands at similar frequencies were observed when the Pt<sub>4</sub><sup>−</sup> ion was reacted with CO<sub>2</sub>, which was also concluded to lead to activation.<sup>31</sup>

From here, we focus on the species [Cu<sub>*n*</sub>C·CO<sub>2</sub>]<sup>−</sup> with *n* = 6 and 7 since their spectra are representative of two modes of adsorption, activated and dissociated. The suspicion that CO<sub>2</sub> adsorbs dissociatively on CCu<sub>7</sub><sup>−</sup> can be verified by reference spectra of carbon monoxide (CO) adsorbed to Cu<sub>7</sub>C<sup>−</sup>, which is compared to the IRMPD spectrum of [Cu<sub>7</sub>C·CO<sub>2</sub>]<sup>−</sup> in Fig. 4b (second panel from the top). For this, we reacted the clusters with CO and recorded IRMPD spectra in the 650–2100 cm<sup>−1</sup> range for the [Cu<sub>*n*</sub>C·CO]<sup>−</sup> (*n* = 4–10) species formed. The resulting spectra for all measured cluster sizes are dominated by a strong band around 2020 cm<sup>−1</sup>, characteristic for the C–O stretch. This band shows an excellent agreement with the bands observed when Cu<sub>7</sub>C<sup>−</sup> is reacted with CO<sub>2</sub> (Fig. 4b, top panel), strengthening the hypothesis that CO<sub>2</sub> adsorbs dissociatively on Cu<sub>*n*</sub>C<sup>−</sup> (*n* = 7–9). In contrast, the mismatch between spectra for [Cu<sub>6</sub>C·CO<sub>2</sub>]<sup>−</sup>

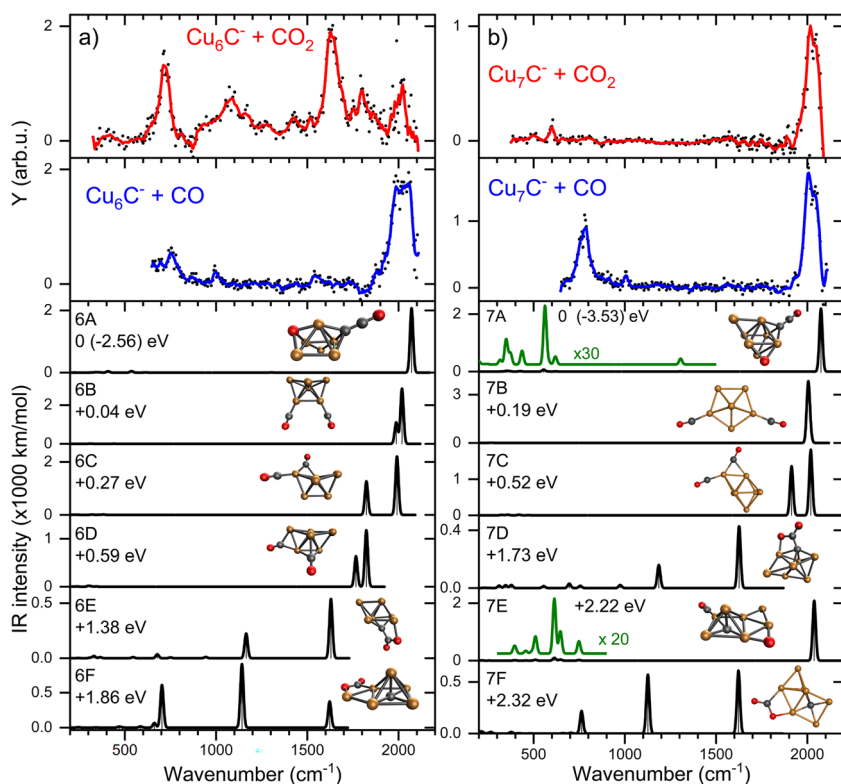


Fig. 4 IRMPD spectra of: (a) Cu<sub>6</sub>C<sup>−</sup>, and (b) Cu<sub>7</sub>C<sup>−</sup>, reacted with CO<sub>2</sub> (red) and CO (blue), and calculated spectra (black) of the lowest energy structure. All calculated spectra are convoluted with a 20 cm<sup>−1</sup> FWHM Gaussian line shape function, and are accompanied by the geometrical structure (Cu, C and O atoms represented by orange, black and red spheres) and relative energy. The green curves are vertical zooms with the multiplication factors indicated. The CO<sub>2</sub> binding energy is given for the lowest energy structure, relative energies for other isomers.





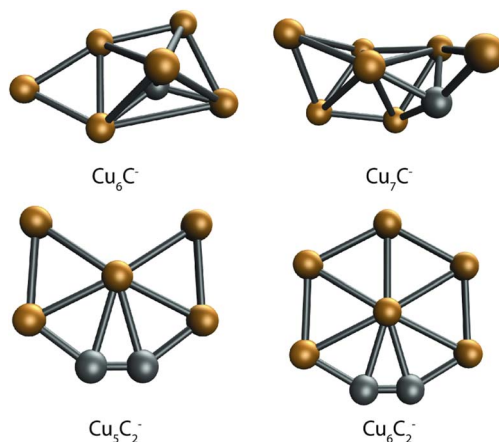


Fig. 5 Lowest energy structures of the single C-doped clusters  $\text{Cu}_6\text{C}^-$  and  $\text{Cu}_7\text{C}^-$ , and double C-doped clusters  $\text{Cu}_5\text{C}_2^-$  and  $\text{Cu}_6\text{C}_2^-$ .

and  $[\text{Cu}_6\text{C}\cdot\text{CO}]^-$  (Fig. 4a) suggests that  $\text{CO}_2$  adsorbs predominantly molecularly on  $\text{Cu}_6\text{C}^-$  and, by extension, also on  $\text{Cu}_{10}\text{C}^-$ .

DFT calculations were performed to further interpret these observations. For this, we first searched for bare  $\text{Cu}_n\text{C}_m^-$  clusters. In our global optimization routine, we have identified the lowest energy structures shown in Fig. 5. The lowest energy structures found are not unlike those predicted for the pure clusters.  $\text{Cu}_6\text{C}^-$  is similar to the predicted  $\text{Cu}_6^-$  octahedron,<sup>41</sup> with the C substituting one of the Cu atoms in the octahedron, and the sixth Cu atom bound to one of the Cu–Cu edges.  $\text{Cu}_7\text{C}^-$  looks like the boat structure proposed for  $\text{Cu}_6^-$ ,<sup>42</sup> with a C bound on a hollow site, and the last Cu atom bound both to the Cu–Cu edge and to the C atom. Interestingly, the structures for  $\text{Cu}_5\text{C}_2^-$  and  $\text{Cu}_6\text{C}_2^-$  are planar and are similar to the structure predicted for pure  $\text{Cu}_5^-$ , a 2D trapezoid.<sup>41,42</sup> In both clusters, the C atoms are bound together in a  $\text{C}_2$  unit that forms one corner of a planar hexagon for  $\text{Cu}_6\text{C}_2^-$ , with one Cu atom missing for  $\text{Cu}_5\text{C}_2^-$ .

Using the structures found for the bare clusters, a search was done for structures of the reaction product of  $\text{Cu}_6\text{C}^-$  and  $\text{Cu}_7\text{C}^-$ . An extensive search has identified over sixty stable structures for each species. Many of these structures have a similar binding motif of C and O atoms to the cluster leading to only minor differences in IR spectra, which are indistinguishable in the currently applied experimental method. Therefore, the structures were grouped, first using their spectral properties only. Visual inspection of all structures per group allowed to conclude that they all shared similar binding motifs. For the  $\text{CO}_2$  reaction products with  $\text{Cu}_6\text{C}^-$ , sixteen unique spectral patterns were identified, for  $\text{Cu}_7\text{C}^-$  only nine. The spectra of the lowest energy representative from each group are compared to the experimental data in Fig. S2.† A selection of the most promising candidates is shown in Fig. 4 (black traces).

In the search, structures are found both with dissociated and molecular  $\text{CO}_2$ , where structures with  $\text{CO}_2$  dissociated are generally lowest in energy. The spectra of structures with dissociated  $\text{CO}_2$  are dominated by high-frequency bands originating from the C–O stretch vibration(s), with frequencies ranging from 1800–





2100  $\text{cm}^{-1}$ , depending on the binding site of the CO. Spectra of clusters with molecularly bound  $\text{CO}_2$  have multiple bands typically at the lower frequencies associated with the  $\text{CO}_2$  bending mode, and the  $\text{C-O}_{\text{bound}}$  and  $\text{C-O}_{\text{free}}$  stretch.

For both  $n = 6$  and 7, the largest number of structures found is with  $\text{CO}_2$  dissociatively adsorbed, where CO is bound in an on-top configuration ( $\mu^1$ ) to a Cu atom, and the O eliminated from  $\text{CO}_2$  bound to another Cu; an example is structure 7E. However, this binding motif is not the energetically most favorable lying at least 1.78 (2.19) eV higher in energy for  $n = 6$  (7) than the lowest energy structure. We attribute this simply to a computational sampling effect, where the probability to find a Cu atom in a  $\text{Cu}_6\text{C}^-$  cluster is six times higher than finding a C atom.

For  $n = 6$ , the spectra of structures from this most populated group are very similar to that of structure 6A, the lowest energy structure, whereas this has a different structural motif. In structure 6A, the cluster structure contains a  $\text{Cu}_5$  square pyramid, with the sixth Cu bridge-bound ( $\mu^2$ ) to one of the edges, and the C bound to a hollow ( $\mu^3$ )  $\text{Cu}_3$  site. Of the dissociated  $\text{CO}_2$ , the CO is  $\mu^1$ -bound to the cluster's C atom, forming a linear C–C–O moiety, and the O to a hollow Cu site. The spectrum has its main band, the CO stretch vibration, close to 2100  $\text{cm}^{-1}$ , or blue-shifted from the observed band frequency by about 60  $\text{cm}^{-1}$ . The same motif of CO binding to the lone C is found for the lowest energy group for  $n = 7$  (e.g. structure 7A). 7A is a  $\text{Cu}_6$  octahedron capped by the seventh Cu and the C, both in  $\mu^3$  configuration. The  $\text{CO}_2$  is dissociated with the single O capping a third octahedron plane, and the CO bound to the C dopant.

For both  $n = 6$  and 7 the second group (e.g. 6B and 7B) is formed by structures where  $\text{CO}_2$  dissociation leads to an O atom migrating to the C dopant atom, forming two CO molecules that are  $\mu^1$ -bound to a Cu. For 6B this is in the form of a  $\text{Cu}_6$  boat structure with the CO molecules attached to the bow and the stern, while for 7B it is a  $\text{Cu}_7$  pentagonal bipyramid. The frequencies of both CO stretch vibrations are close to each other resulting in one merged vibrational band, which is found at frequencies of about 2000  $\text{cm}^{-1}$ , slightly lower than that for the C–C–O group in 6A and 7A. Group 3 (e.g. 6C/7C) is characterized by two CO molecules, with one  $\mu^1$ - and the other  $\mu^2$ -bound. In 7C, the same capped octahedron is recognized, with the bridge-bound CO close to the on-top CO. In this case, two distinct C–O stretch bands are seen, one around 2000  $\text{cm}^{-1}$  for the  $\mu^1$  bound CO, and one around 1900  $\text{cm}^{-1}$  for the  $\mu^2$  bound CO. For  $n = 6$ , group 4 has CO molecules bound in  $\mu^2$  and  $\mu^3$  configurations, with again clearly two distinct bands, now at 1800 and 1900  $\text{cm}^{-1}$ , consistent with a weakening of the C–O bond when it coordinates to multiple Cu atoms. An interesting motif found is the linking of two CO molecules resulting in an O–C–C–O chain. However, for both cluster sizes, this last group is lowly populated, relatively high in energy, and presents no match for the experimental spectrum.

Structures with molecularly bound  $\text{CO}_2$  are typically much higher in energy ( $>1.4$  eV) for both  $n = 6$  and 7. The structures found are always di- $\sigma$ -bound *via* the C and the O. Formation of a C–C bond is favorable resulting in the preferential binding of the  $\text{CO}_2$  carbon atom to the cluster's carbon atom, with one of the O atoms binding to a Cu atom. The lowest energy structures displaying this binding motif are 6E and 7D.

Structures are assigned based on the comparison between calculated and experimental spectra. The IRMPD spectrum of  $[\text{Cu}_6\text{C}\cdot\text{CO}_2]^-$  shows two major



bands at 718 and 1630  $\text{cm}^{-1}$  with weaker bands at 1094, 1426, 1802, and 2016  $\text{cm}^{-1}$ . This number of bands cannot be explained by a single structure. The major band at 718  $\text{cm}^{-1}$  agrees best with the  $\text{CO}_2$  bending mode predicted at 705  $\text{cm}^{-1}$  for structure 6F, where  $\text{CO}_2$  is intact, but bent as a result of charge transfer. The  $\text{CO}_2$  molecule is bound with a C and the O to two neighboring Cu atoms in a bidentate bridging configuration. Two more intense bands are predicted at 1141 and 1620  $\text{cm}^{-1}$  offering a good match for the experimental bands at 1094 and 1630  $\text{cm}^{-1}$ . These correspond to the C–O stretching vibrations involving the bound and free O atoms, respectively. Although the band frequencies of 6F match the experiment very well, the relative intensities are less convincing. The experimental band at 718  $\text{cm}^{-1}$  has the highest intensity, even though it does not dominate any of the calculated spectra. We do not have a good explanation for this observation; we can speculate that it is related to the excitation mechanism in IRMPD spectroscopy, which may cause discrepancies with calculated intensities.

The search for low energy structures for  $\text{Cu}_6\text{C}^-$  yielded a  $\text{Cu}_5$  square pyramid structure shown in Fig. 5, with the C atom fourfold coordinated to the base, and an additional Cu atom  $\mu^2$ -bound on one of the edges. In structure 6F, this structure is retained, making this a likely entrance complex. Despite the higher energy of structure 6F (+1.86 eV relative to the lowest energy structure) it is the easiest formed. The formation of other more stable isomers necessarily proceeds *via* either C–O bond cleavage or structural rearrangement of the cluster. Both processes require additional energy to overcome a barrier associated with the transition state.

The depletion spectrum of  $[\text{Cu}_6\text{C}\cdot\text{CO}_2]^-$  (Fig. S1†) does not rule out a mixture of different isomers present in the molecular beam, since none of the bands reach 100% depletion. The enhanced intensity of the 1630  $\text{cm}^{-1}$  experimental band could then potentially be explained by the presence of an isomer like 6E with predicted bands at 1163 and 1629  $\text{cm}^{-1}$ . Structure 6E appears also relatively easily formed as an entrance complex, where  $\text{CO}_2$  also binds in a bidentate bridging configuration, now with the C to the cluster's carbon atom. However, the bare cluster's bridging Cu is now bound on a hollow site.

The dominant experimental bands can thus be explained by molecularly adsorbed  $\text{CO}_2$ , but minor bands above 1750  $\text{cm}^{-1}$  more likely originate from the carbonyl C–O stretch, resulting from  $\text{CO}_2$  dissociation. The band at 1802  $\text{cm}^{-1}$  might be due to structure 6C's 1825  $\text{cm}^{-1}$  predicted mode but could also be assigned to the doublet from structure 6D at 1764 and 1825  $\text{cm}^{-1}$ , which could have merged into one band due to band broadening. The 2016  $\text{cm}^{-1}$  band could be the second band of structure 6C at 1990  $\text{cm}^{-1}$  or 6A and 6B's bands at 2069 and 2018  $\text{cm}^{-1}$ , respectively. The offset for 6A makes 6B, 6C and 6D the more likely candidates to explain the high-frequency bands.

All in all, it can be concluded that  $\text{CO}_2$  binds mostly molecularly to  $\text{Cu}_6\text{C}^-$ , but in an activated form *via* the C atom either to C or to Cu atoms. Dissociation may occur, but it is certainly not the dominant motif, which is underlined by the significantly higher predicted IR intensities of the carbonyl C–O stretch modes.

This dominance of molecular binding is in sharp contrast to what happens after adsorption of  $\text{CO}_2$  on  $\text{Cu}_7\text{C}^-$ . The IRMPD spectrum of  $[\text{Cu}_7\text{C}\cdot\text{CO}_2]^-$  has one dominant band at 2033  $\text{cm}^{-1}$  and a low-intensity band at 598  $\text{cm}^{-1}$ . From a comparison with low-energy isomers, it is quite clear that  $\text{CO}_2$  is dissociated since no bands associated with activated complexes (7D and 7F) are present in the



experimental spectrum. Structure 7C has two CO binding motifs, and its spectrum has separate bands at 1915 ( $\mu^2$ , Cu–Cu) and 2017  $\text{cm}^{-1}$  ( $\mu^1$ , Cu). Because this does not match the experimental spectrum, we must look for structures with only  $\mu^1$  binding. Spectra calculated for such structures (7A, 7B, and 7E) are dominated by one band, depending on the adsorption site of CO, at 2078 ( $\mu^1$  to C), 2017 (twice  $\mu^1$  to Cu) and 2038  $\text{cm}^{-1}$  ( $\mu^1$  to Cu), respectively. Each of them could explain the main experimental band at 2033  $\text{cm}^{-1}$ . The low-intensity band at 598  $\text{cm}^{-1}$  could be due to the weak bands around 558 and 600  $\text{cm}^{-1}$  for structures 7A and 7E, respectively. These bands are more than twenty times lower in intensity than the C–O stretch. We therefore assign the spectrum to either 7A or 7E, corresponding to structures where the CO formed from dissociating  $\text{CO}_2$  is  $\mu^1$ -bound either to the cluster's C or Cu atom, and O bound separately to the cluster. Both structures appear not easily formed, because the lowest energy structure for  $\text{Cu}_7\text{C}^-$  (Fig. 5) requires substantial re-arrangement.

### $\text{CO}_2$ activation by $\text{Cu}_n\text{C}_2^-$

If  $\text{CO}_2$  is reacted with Cu clusters containing a second carbon, the picture changes. The spectra for the  $[\text{Cu}_n\text{C}_2\cdot\text{CO}_2]^-$  ( $n = 3\text{--}8$ ) species are presented in Fig. 3 (right panels). Due to a different production efficiency for clusters with two C atoms, a slightly different range of  $n$  is presented. In contrast to the  $\text{Cu}_n\text{C}^-$  species, where only  $[\text{Cu}_6\text{C}\cdot\text{CO}_2]^-$  and  $[\text{Cu}_{10}\text{C}\cdot\text{CO}_2]^-$  show molecular adsorption, all spectra except that for  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$  show bands around 740, 1150, and 1650  $\text{cm}^{-1}$  indicating activated, but molecular adsorption of  $\text{CO}_2$ . For all these species, bands above 1800  $\text{cm}^{-1}$ , attributed to dissociative  $\text{CO}_2$  adsorption, have disappeared, suggesting that only molecularly bound  $\text{CO}_2$  complexes are left. Only the spectrum of  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$  shows an intense band at 2034  $\text{cm}^{-1}$ , suggesting dissociative adsorption. From this, it can be concluded that, overall, the addition of the second C atom reduces the cluster reactivity.

Again, we selected two cluster sizes for DFT calculations,  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$  and  $[\text{Cu}_6\text{C}_2\cdot\text{CO}_2]^-$ . From the glancing overview in Fig. 3 they are representative for dissociative and molecular binding of  $\text{CO}_2$ . The comparison of the spectra for these structures with spectra of the clusters reacted with CO confirms this conclusion, because the 2034  $\text{cm}^{-1}$  band for  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$  perfectly matches that observed for  $[\text{Cu}_5\text{C}_2\cdot\text{CO}]^-$ . In contrast, the spectrum for  $[\text{Cu}_6\text{C}_2\cdot\text{CO}]^-$  does not show any counterpart for the bands dominating the spectrum of  $[\text{Cu}_6\text{C}_2\cdot\text{CO}_2]^-$ .

The calculated structures were again categorized following their spectral and adsorption motifs, as illustrated in Fig. 6. The full list of the lowest energy structures of the identified groups can be found in Fig. S3.† Interestingly, for higher carbon loading, the most common motif found is still the dissociation of  $\text{CO}_2$  to CO and O (5C and 6.2C), both bound to Cu atoms. The lowest energy structures 5A and 6.2A are formed by the adsorption of CO to one of the cluster's C atoms and O to the other, forming a C–C–O and a CO moiety. These structures are comparable to the CO motif of  $\text{Cu}_6\text{C}^-$  and  $\text{Cu}_7\text{C}^-$ , suggesting it is overall more favorable for  $\text{CO}_2$  to dissociate and bind to the C atoms of the cluster, rather than to Cu.

The experimental spectrum of  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$  is dominated by the strong band at 2035  $\text{cm}^{-1}$  and has two more bands at 1667 and 1810  $\text{cm}^{-1}$ . The maximum depletion observed ( $\sim 45\%$ ) allows room for assignment to multiple isomers. All



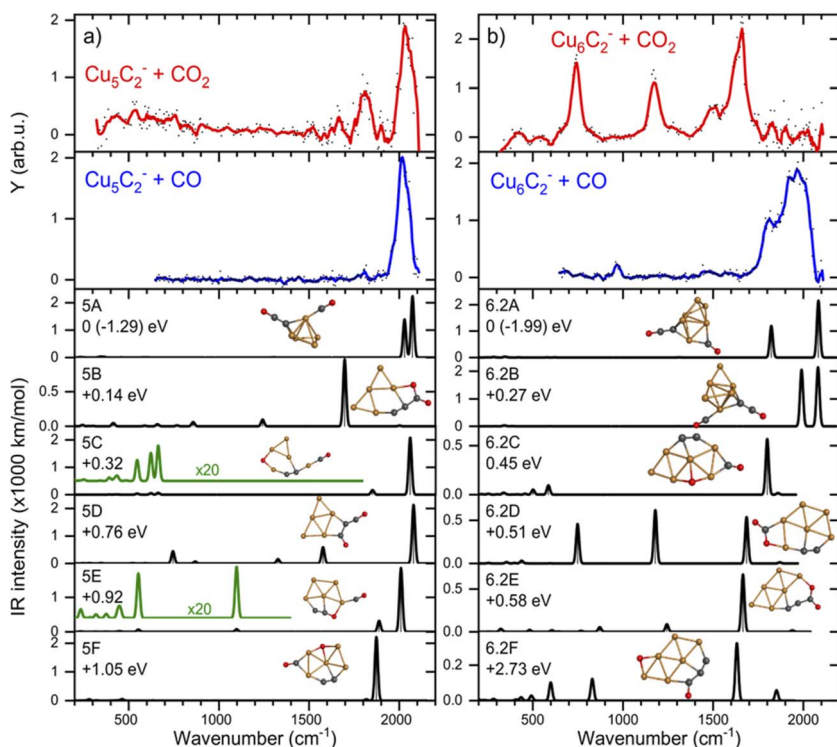


Fig. 6 IRMPD spectra of (a)  $\text{Cu}_5\text{C}_2^-$  and (b)  $\text{Cu}_6\text{C}_2^-$  reacted with  $\text{CO}_2$  (red) and  $\text{CO}$  (blue), and calculated spectra (black) of the lowest energy structure. For details, see caption Fig. 4.

structures shown could potentially be present in the molecular beam since they all have bands that might overlap with the experimentally detected. The experimental band at  $2035\text{ cm}^{-1}$  could be explained either by structure 5A with two close by bands predicted at  $2077$  and  $2027\text{ cm}^{-1}$ , or by structures 5C, 5D, and 5E with bands at  $2063$ ,  $2078$ , and  $2012\text{ cm}^{-1}$ , respectively. The second band, at  $1810\text{ cm}^{-1}$ , could be explained by the main band of structure 5F at  $1865\text{ cm}^{-1}$ , or by the minor bands predicted for structures 5C and 5E. The only serious contender for the weakest band observed at  $1667\text{ cm}^{-1}$  is structure 5B with the band at  $1698\text{ cm}^{-1}$ . All except for 5B, have  $\text{CO}_2$  adsorbed dissociatively on the cluster. 5B has molecularly adsorbed  $\text{CO}_2$  bound with the one of the C atoms attached to one of the cluster's C atoms, and the O to a Cu.

If we compare the structures shown in Fig. 6a to the lowest energy structure for  $\text{Cu}_5\text{C}_2^-$ , predicted to have a 2D, wheel-like structure, it appears that all structures apart from 5A could be formed without all too large structural re-arrangements of the original cluster: all retain a planar structure with the two C atoms of the bare clusters close together. Only the formation of 5A upon  $\text{CO}_2$  adsorption requires a major structural re-arrangement.

In contrast to the spectrum of  $[\text{Cu}_5\text{C}_2\cdot\text{CO}_2]^-$ , the spectrum of  $[\text{Cu}_6\text{C}_2\cdot\text{CO}_2]^-$  does not exhibit any bands above  $1780\text{ cm}^{-1}$ , which is indicative that  $\text{CO}_2$  is adsorbed molecularly. Therefore, structures 6.2A, 6.2B and 6.2C can be ruled out since they all have high-intensity bands at  $1800\text{ cm}^{-1}$  or above. Three of the four



experimental bands (742, 1173, and  $1648\text{ cm}^{-1}$ ) could quite well be explained by isomer 6.2D with bands at 748, 1179, and  $1685\text{ cm}^{-1}$ . The band at  $1648\text{ cm}^{-1}$  could also be explained by the  $1648\text{ cm}^{-1}$  band of structure 6.2E or by structure 6.2F's  $1634\text{ cm}^{-1}$  band, but these structures lack intense bands at lower frequencies. Only the experimental band at  $1484\text{ cm}^{-1}$ , a shoulder of the  $1648\text{ cm}^{-1}$  band, cannot be explained by isomer 6.2D. Interestingly, it appears quite similar to the weaker band at  $1426\text{ cm}^{-1}$  in the  $[\text{Cu}_6\text{C}\cdot\text{CO}_2]^-$  spectrum, which may have a similar origin. Another parallel drawn from the spectrum of  $[\text{Cu}_6\text{C}\cdot\text{CO}_2]^-$  is that the relative intensities of the middle band are not reflecting the calculated ratios.

## Reactive potential energy surface

It is now of interest to understand what factors could determine dissociation or lack thereof. For this, we attempted to calculate reaction pathways for two representative clusters. The complexity associated with reconstructing the reactive pathway of  $\text{CO}_2$  adsorption and subsequent activation over carbon-doped Cu clusters is enormous. First, as experimental evidence for the structures of the bare clusters is unknown, the starting point is ill-defined. Nevertheless, using the minima found in Fig. 5, we calculated a reaction pathway for  $\text{CO}_2$  dissociation. It is clear that the structural phase-space for  $\text{CO}_2$  initial adsorption is large, and the pathways to dissociation are plenty. We therefore limit ourselves to potential pathways that could illuminate whether there could exist a difference in barrier for even or odd numbers of Cu atoms.

In the top panel of Fig. 7, the adsorption and subsequent dissociation of  $\text{CO}_2$  over  $\text{Cu}_6\text{C}^-$  is shown. Adsorption leads to the formation of structure 6F, already thought to be an entrance complex, with an adsorption energy of 0.73 eV. The  $\text{CO}_2$  is adsorbed *via* the C to one of the Cu atoms forming the base of the octahedron, and the O atom to the capping extra Cu atom. From here, CO is abstracted towards the base Cu atom, after which it is bound to the next Cu–Cu bridge, overall gaining little energy with respect to the entrance complex. The transition state associated with abstracting the CO is relatively high at 1.18 eV above the reactants. Such a barrier is insurmountable, certainly under the room-temperature near-thermal conditions of the reaction channel used here.

The bottom panel of Fig. 7 shows the same reaction path, now calculated for  $\text{CO}_2$  adsorbing onto  $\text{Cu}_7\text{C}^-$ . The entrance complex found is much higher in energy than anything shown in Fig. 4b, at about 2.5 eV higher than structure 7A, the lowest energy structure. The cluster is an octahedral  $\text{Cu}_5\text{C}$ , with the sixth Cu (denoted Cu(6)) bridge-bound to a Cu–Cu edge, and the seventh to the newly formed Cu–Cu(6) edge.  $\text{CO}_2$  is adsorbed *via* its C atom to an octahedron Cu atom, and *via* an O atom to the other Cu–Cu(6) edge. CO abstraction then leads to an energetically still not very favorable structure with the CO bound on top of a Cu atom, and the O atom on a hollow Cu–Cu–Cu site. The initial adsorption energy of  $\text{CO}_2$  onto  $\text{Cu}_7\text{C}^-$  is with 0.93 eV not much different from that of  $\text{Cu}_6\text{C}^-$ . In contrast, the dissociation reaction over  $\text{Cu}_7\text{C}^-$  is much more facile than over  $\text{Cu}_6\text{C}^-$ , and with an energy barrier 0.55 eV lower than the energy of the reactants, this dissociation reaction is well possible.

These two reaction paths are by no means a complete description of the reactions taking place. However, they do allow to draw initial conclusions. (1) The



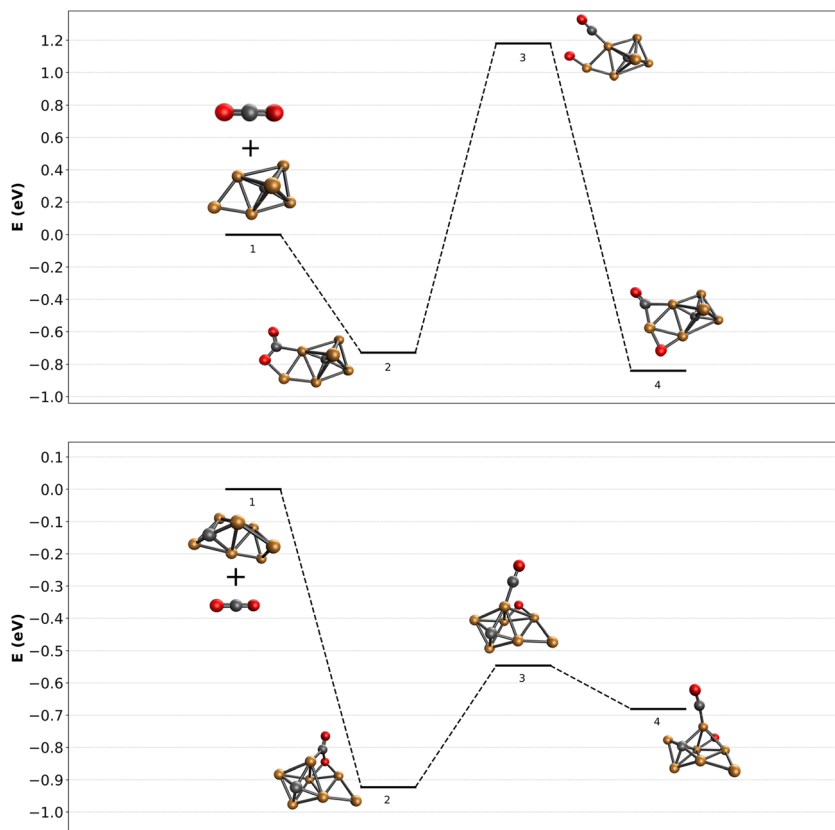


Fig. 7 Reactive potential energy surface for CO<sub>2</sub> dissociation over the lowest energy structures found for Cu<sub>6</sub>C<sup>-</sup> and Cu<sub>7</sub>C<sup>-</sup>, calculated at the TPSSH/def2-TZVPD level of theory. Energies (in eV) are given with respect to the bare clusters and free CO<sub>2</sub>.

observation of dominant molecular adsorption in the experimental spectrum of [Cu<sub>6</sub>C·CO<sub>2</sub>]<sup>-</sup> is consistent with the high barrier calculated from structure 6F in Fig. 7; (2) finding a dissociation barrier below the energy of the reactants for Cu<sub>7</sub>C<sup>-</sup> demonstrates that dissociation should occur, also consistent with the observed spectrum. It may not be this pathway, as lower barrier pathways may exist, but if an exothermic reaction with a barrier below the reactants exists, the system should find it.

So what is now the influence of the carbon atom on the dissociation propensity? We recall that for Cu<sub>n</sub>C<sup>-</sup> the dominant adsorption form is dissociative and for Cu<sub>n</sub>C<sub>2</sub><sup>-</sup> molecular. If extra carbon atoms have a decisive influence, one would compare the outcome of the CO<sub>2</sub> adsorption reaction for clusters with the same number of atoms, where Cu atoms are exchanged for C atoms. For this comparison, we evaluate the spectra in Fig. 3, comparing Cu<sub>6</sub>C<sup>-</sup> with Cu<sub>5</sub>C<sub>2</sub><sup>-</sup>, Cu<sub>7</sub>C<sup>-</sup> with Cu<sub>6</sub>C<sub>2</sub><sup>-</sup>, and so on. If anything, one sees that this comparison gives opposite outcomes: Cu<sub>6</sub>C<sup>-</sup> molecular, Cu<sub>5</sub>C<sub>2</sub><sup>-</sup> dissociative; Cu<sub>7</sub>C<sup>-</sup> dissociative, Cu<sub>6</sub>C<sub>2</sub><sup>-</sup> molecular; Cu<sub>8</sub>C<sup>-</sup> dissociative, Cu<sub>7</sub>C<sub>2</sub><sup>-</sup> inconclusive; Cu<sub>9</sub>C<sup>-</sup> dissociative, Cu<sub>8</sub>C<sub>2</sub><sup>-</sup> molecular. Then, if we compare clusters with the same number of Cu atoms: Cu<sub>6</sub>C<sup>-</sup> and Cu<sub>6</sub>C<sub>2</sub><sup>-</sup> molecular, Cu<sub>7</sub>C<sup>-</sup> dissociative, Cu<sub>7</sub>C<sub>2</sub><sup>-</sup> inconclusive;





$\text{Cu}_8\text{C}^-$  dissociative,  $\text{Cu}_8\text{C}_2^-$  molecular. The only trend, if one may call it this: the addition of the second carbon to the cluster inhibits the dissociative adsorption for all cluster sizes except for  $n = 5$ . We can only speculate that the addition of an extra C atom, which has the higher electron affinity of C (2.55) compared to Cu (1.90),<sup>43</sup> leads to a decrease of the charge located on the Cu atoms thereby reducing the electron donation from the cluster into the  $\text{CO}_2$  antibonding orbital. Of course, such a hypothesis requires a more detailed investigation, including spectroscopic characterization of  $\text{CO}_2$  activation by the pure  $\text{Cu}_n^-$  clusters that was elusive in this work.

## Conclusion

IRMPD spectroscopy of the  $\text{CO}_2$  adsorbed on the anionic copper carbides reveals a size-dependent bonding nature. Single-carbon doped Cu clusters  $\text{Cu}_n\text{C}^-$  with  $n = 6$  and 10 show predominantly activated adsorption, but dissociative adsorption of  $\text{CO}_2$  for  $n = 7-9$ . These results were verified with control experiments of CO adsorbed on the same cluster sizes and with DFT calculations. The exact position of the C and O atoms on the clusters could not be determined precisely, since the bands for specific structures are very similar in frequency. Therefore, only the main binding motifs have been analyzed. Doubly-carbon doped Cu clusters  $\text{Cu}_n\text{C}_2^-$  with  $n = 3-8$  show predominantly molecular adsorption, excepting  $\text{Cu}_5\text{C}_2^-$  which shows dissociative adsorption of  $\text{CO}_2$ . DFT calculations of the dissociation reaction of  $\text{CO}_2$  over  $\text{Cu}_6\text{C}^-$  and  $\text{Cu}_7\text{C}^-$  are consistent with the observed IR spectra, showing only activation for the former and dissociation for the latter. To understand why the addition of a second C atom apparently throttles  $\text{CO}_2$  dissociation requires further extensive computational work, evaluating reactive pathways over other cluster compositions. We speculate that the higher electron affinity of C relative to that of Cu will reduce the capacity of Cu atoms in higher C/Cu ratio clusters to donate electron density to  $\text{CO}_2$ , reducing the activation capabilities.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors acknowledge financial support from the Netherlands Organization for Scientific Research (NWO) under grant no. 739.017.008 (Mat4Sus), and the European Union's Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie grant agreement No. 955650. We further thank NWO for the support of the FELIX Laboratory and for CPU time at the Dutch National Supercomputers Cartesius and Snellius (2021.055). TH is grateful for the János Bolyai Research Scholarship (BO/00642/21/7) of the Hungarian Academy of Sciences. OVL acknowledges the Austrian Science Fund (FWF) for a Lise Meitner Scholarship (M3229-N). We thank Prof. László Nyulász for fruitful discussions.

## Notes and references

- 1 S. Xie, Q. Zhang, G. Liu and Y. Wang, *Chem. Commun.*, 2016, 52, 35–59.





- 2 M. Behrens, F. Studt, I. Kasatkin, S. Kuhl, M. Havecker, F. Abild-Pedersen, S. Zander, F. Girgsdies, P. Kurr, B.-L. Kniep, M. Tovar, R. W. Fischer, J. K. Nørskov and R. Schlögl, *Science*, 2012, **336**, 893–897.
- 3 M. V. Twigg and M. S. Spencer, *Top. Catal.*, 2003, **22**, 191–203.
- 4 H. H. Hwu and J. G. Chen, *Chem. Rev.*, 2005, **105**, 185–212.
- 5 S. Posada-Pérez, F. Viñes, J. A. Rodriguez and F. Illas, *Top. Catal.*, 2015, **58**, 159–173.
- 6 Q. Zhang, L. Pastor-Pérez, S. Gu and T. R. Reina, *Catalysts*, 2020, **10**, 1–23.
- 7 A. L. Stottlemeyer, T. G. Kelly, Q. Meng and J. G. Chen, *Surf. Sci. Rep.*, 2012, **67**, 201–232.
- 8 M. D. Porosoff, S. Kattel, W. Li, P. Liu and J. G. Chen, *Chem. Commun.*, 2015, **51**, 6988–6991.
- 9 X. Liu, C. Kunkel, P. Ramírez De La Piscina, N. Homs, F. Viñ and F. Illas, *ACS Catal.*, 2017, **7**, 4323–4335.
- 10 J. A. Rodriguez, J. Evans, L. Feria, A. B. Vidal, P. Liu, K. Nakamura and F. Illas, *J. Catal.*, 2013, **307**, 162–169.
- 11 P. Liu and J. A. Rodriguez, *J. Chem. Phys.*, 2004, **120**, 5414–5423.
- 12 L. K. Ono, D. Sudfeld and B. Roldan Cuenya, *Surf. Sci.*, 2006, **600**, 5041–5050.
- 13 J. A. Rodriguez and F. Illas, *Phys. Chem. Chem. Phys.*, 2012, **14**, 427–438.
- 14 S. Posada-Pérez, P. J. Ramírez, J. Evans, F. Viñes, P. Liu, F. Illas and J. A. Rodriguez, *J. Am. Chem. Soc.*, 2016, **138**, 8269–8278.
- 15 A. B. Vidal, L. Feria, J. Evans, Y. Takahashi, P. Liu, K. Nakamura, F. Illas and J. A. Rodriguez, *J. Phys. Chem. Lett.*, 2012, **3**, 2275–2280.
- 16 J. A. Rodriguez, D. Stacchiola, S. Senanayake, P. Liu and J. Evans, *ACS Catal.*, 2015, **5**, 6696–6706.
- 17 X. Zhang, E. Lim, S. K. Kim and K. H. Bowen, *J. Chem. Phys.*, 2015, **143**, 174305.
- 18 D. W. Arnold, S. E. Bradforth, E. H. Kim and D. M. Neumark, *J. Chem. Phys.*, 1995, **102**, 3510–3518.
- 19 B. J. Knurr and J. M. Weber, *J. Phys. Chem. A*, 2014, **118**, 10246–10251.
- 20 B. J. Knurr and J. M. Weber, *J. Phys. Chem. A*, 2014, **118**, 8753–8757.
- 21 B. J. Knurr and J. M. Weber, *J. Am. Chem. Soc.*, 2012, **134**, 18804–18808.
- 22 A. D. Boese, H. Schneider, A. N. Glöß and J. M. Weber, *J. Chem. Phys.*, 2005, **122**, 154301.
- 23 B. J. Knurr and J. M. Weber, *J. Phys. Chem. A*, 2013, **117**, 10764–10771.
- 24 M. C. Thompson, L. G. Dodson and J. M. Weber, *J. Phys. Chem. A*, 2017, **121**, 4132–4138.
- 25 M. C. Thompson, J. Ramsay and J. M. Weber, *J. Phys. Chem. A*, 2017, **121**, 7534–7542.
- 26 M. C. Thompson and J. M. Weber, *J. Phys. Chem. A*, 2018, **122**, 3772–3779.
- 27 B. J. Knurr and J. M. Weber, *J. Phys. Chem. A*, 2014, **118**, 4056–4062.
- 28 J. M. Weber, *Int. Rev. Phys. Chem.*, 2014, **33**, 489–519.
- 29 P. A. Hintz and K. M. Ervin, *J. Chem. Phys.*, 1995, **103**, 7897–7906.
- 30 J. Ho, K. M. Ervin and W. C. Lineberger, *J. Chem. Phys.*, 1990, **93**, 6987–7002.
- 31 A. E. Green, J. Justen, W. Schöllkopf, A. S. Gentleman, A. Fielicke and S. R. Mackenzie, *Angew. Chem., Int. Ed.*, 2018, **57**, 14822–14826.
- 32 A. Yanagimachi, K. Koyasu, D. Y. Valdivielso, S. Gewinner, W. Schöllkopf, A. Fielicke and T. Tsukuda, *J. Phys. Chem. C*, 2016, **120**, 14209–14215.
- 33 T. G. Dietz, M. A. Duncan, D. E. Powers and R. E. Smalley, *J. Chem. Phys.*, 1981, **74**, 6511–6512.



- 34 J. M. Bakker, V. J. F. Lapoutre, B. Redlich, J. Oomens, B. G. Sartakov, A. Fielicke, G. von Helden, G. Meijer and A. F. G. van der Meer, *J. Chem. Phys.*, 2010, **132**, 074305.
- 35 Y. Shao, Z. Gan, E. Epifanovsky, A. T. B. Gilbert, M. Wormit, J. Kussmann, A. W. Lange, A. Behn, J. Deng, X. Feng, D. Ghosh, M. Goldey, P. R. Horn, L. D. Jacobson, I. Kaliman, R. Z. Khaliullin, T. Kuš, A. Landau, J. Liu, E. I. Proynov, Y. M. Rhee, R. M. Richard, M. A. Rohrdanz, R. P. Steele, E. J. Sundstrom, H. L. Woodcock, P. M. Zimmerman, D. Zuev, B. Albrecht, E. Alguire, B. Austin, G. J. O. Beran, Y. A. Bernard, E. Berquist, K. Brandhorst, K. B. Bravaya, S. T. Brown, D. Casanova, C.-M. Chang, Y. Chen, S. H. Chien, K. D. Closser, D. L. Crittenden, M. Diedenhofen, R. A. DiStasio, H. Do, A. D. Dutoi, R. G. Edgar, S. Fatehi, L. Fusti-Molnar, A. Ghysels, A. Golubeva-Zadorozhnaya, J. Gomes, M. W. D. Hanson-Heine, P. H. P. Harbach, A. W. Hauser, E. G. Hohenstein, Z. C. Holden, T.-C. Jagau, H. Ji, B. Kaduk, K. Khistyayev, J. Kim, J. Kim, R. A. King, P. Klunzinger, D. Kosenkov, T. Kowalczyk, C. M. Krauter, K. U. Lao, A. D. Laurent, K. V. Lawler, S. V. Levchenko, C. Y. Lin, F. Liu, E. Livshits, R. C. Lochan, A. Luenser, P. Manohar, S. F. Manzer, S.-P. Mao, N. Mardirossian, A. V. Marenich, S. A. Maurer, N. J. Mayhall, E. Neuscamman, C. M. Oana, R. Olivares-Amaya, D. P. O'Neill, J. A. Parkhill, T. M. Perrine, R. Peverati, A. Prociuk, D. R. Rehn, E. Rosta, N. J. Russ, S. M. Sharada, S. Sharma, D. W. Small, A. Sodt, T. Stein, D. Stück, Y.-C. Su, A. J. W. Thom, T. Tsuchimochi, V. Vanovschi, L. Vogt, O. Vydrov, T. Wang, M. A. Watson, J. Wenzel, A. White, C. F. Williams, J. Yang, S. Yeganeh, S. R. Yost, Z.-Q. You, I. Y. Zhang, X. Zhang, Y. Zhao, B. R. Brooks, G. K. L. Chan, D. M. Chipman, C. J. Cramer, W. A. Goddard, M. S. Gordon, W. J. Hehre, A. Klamt, H. F. Schaefer, M. W. Schmidt, C. D. Sherrill, D. G. Truhlar, A. Warshel, X. Xu, A. Aspuru-Guzik, R. Baer, A. T. Bell, N. A. Besley, J.-D. Chai, A. Dreuw, B. D. Dunietz, T. R. Furlani, S. R. Gwaltney, C.-P. Hsu, Y. Jung, J. Kong, D. S. Lambrecht, W. Liang, C. Ochsenfeld, V. A. Rassolov, L. V. Slipchenko, J. E. Subotnik, T. Van Voorhis, J. M. Herbert, A. I. Krylov, P. M. W. Gill and M. Head-Gordon, *Mol. Phys.*, 2015, **113**, 184–215.
- 36 F. Liu, E. Proynov, J.-G. Yu, T. R. Furlani and J. Kong, *J. Chem. Phys.*, 2012, **137**, 114104.
- 37 O. V. Lushchikova, M. Szalay, H. Tahmasbi, L. B. F. Juurlink, J. Meyer, T. Höltzl and J. M. Bakker, *Phys. Chem. Chem. Phys.*, 2021, **23**, 26661–26673.
- 38 J. B. A. Davis, F. Baletto and R. L. Johnston, *J. Phys. Chem. A*, 2015, **119**, 9703–9709.
- 39 N. Mina-Camilde, C. I. Manzanares and J. F. Caballero, *J. Chem. Educ.*, 1996, **73**, 804.
- 40 K. O. Hartman and I. C. Hisatsune, *J. Chem. Phys.*, 1966, **44**, 1913–1918.
- 41 S. Li, M. M. G. Alemany and J. R. Chelikowsky, *J. Chem. Phys.*, 2006, **125**, 034311.
- 42 K. Jug, B. Zimmermann, P. Calaminici and A. M. Köster, *J. Chem. Phys.*, 2002, **116**, 4497.
- 43 A. Louis Allred, *J. Inorg. Nucl. Chem.*, 1961, **17**, 215–221.

