

Cite this: *Mater. Adv.*, 2022,  
3, 8449

## g-C<sub>3</sub>N<sub>4</sub>/dendritic fibrous nanosilica doped with potassium for photocatalytic CO<sub>2</sub> reduction†

Sushma A. Rawool,<sup>a</sup> Yusuf Kar<sup>b</sup> and Vivek Polshettiwar \*<sup>a</sup>

Photocatalytic CO<sub>2</sub> conversion is a promising process for the reduction of CO<sub>2</sub> into useful chemicals and fuels using solar energy. In this work, we have synthesized potassium-doped g-C<sub>3</sub>N<sub>4</sub> coated over dendritic fibrous nanosilica (K-CN/DFNS) and studied the photocatalytic CO<sub>2</sub> conversion under visible light illumination. K-CN/DFNS was synthesized by heating KOH-treated melamine in a vacuum-sealed quartz tube by varying the amounts of potassium salt. The scanning electron microscopy images confirmed the coating of potassium-doped g-C<sub>3</sub>N<sub>4</sub> over DFNS, while the absorption spectra show extended absorption in the visible region and redshift in the bandgap as compared to the undoped CN/DFNS. XPS analysis further confirms the interaction of potassium ions with g-C<sub>3</sub>N<sub>4</sub>. During the photocatalytic CO<sub>2</sub> conversion, the selectivity towards the formation of hydrogen (from water splitting) was the highest for the g-C<sub>3</sub>N<sub>4</sub> and CN/DFNS catalysts, whereas no hydrogen generation was observed using the potassium-doped catalysts. The highest methane yield observed was 1.7 μmol g<sup>-1</sup> for g-C<sub>3</sub>N<sub>4</sub> in 4 h using K-CN/DFNS-2 (with 6 wt% of potassium ions). The high activity and improved selectivity of K-CN/DFNS were due to the extended absorption in the visible region, better separation of charge carriers, shifting of the conduction band and valence band positions towards positive potentials, and moderate adsorption of CO<sub>2</sub> molecules on its surface.

Received 5th July 2022,  
Accepted 16th September 2022

DOI: 10.1039/d2ma00809b

rsc.li/materials-advances

## Introduction

The generation of greenhouse gases is a major concern in order to protect the climate from global warming. Fossil fuels produce a large amount of CO<sub>2</sub> during their burning and an increase in CO<sub>2</sub> level of up to 590 ppm can result in a rise in the global temperature by 1.9 °C.<sup>1</sup> Thus, different methodologies have been developed to tackle the issue of excessive anthropogenic CO<sub>2</sub> in the environment.<sup>2–4</sup> One of the best methods is photocatalytic CO<sub>2</sub> conversion using solar energy, where a photocatalyst harvests solar energy to convert CO<sub>2</sub> into valuable fuels like methane, methanol, formic acid *etc.*, using water as a proton source.<sup>3,4</sup> Different metal oxides, sulfides, nitrides, and oxynitrides have been studied as photocatalysts.<sup>3–6</sup> Among them, metal-free organic polymeric graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) has attracted tremendous attention because of its low bandgap of 2.7 eV, its inexpensive, environmentally friendly, and chemically inert nature and also the fact that the reduction potential of CO<sub>2</sub> conversion falls within its bandgap.<sup>7,8</sup> It can be synthesized using

nitrogen-rich molecules like urea, melamine, cyanamide, dicyandiamide *etc.*<sup>7–11</sup>

Scheme S1 (ESI†) shows the presence of a different type of nitrogen in g-C<sub>3</sub>N<sub>4</sub>, which helps in CO<sub>2</sub> adsorption and activation because of the lone pair of electrons present on it. The pyridinic nitrogen group shows Lewis basicity because of the presence of a lone pair of electrons and thus helps in the adsorption and activation of CO<sub>2</sub> molecules.<sup>11</sup> This nitrogen has a higher negative charge as it can retain the lone pair of electrons in a planar structure and thus can bind CO<sub>2</sub> more effectively than other types of nitrogen present in g-C<sub>3</sub>N<sub>4</sub>. Quaternary graphitic nitrogen shows Lewis acidity as the electrons from its π\* antibonding orbital are less accessible for CO<sub>2</sub> binding. Also, the other types of nitrogen species formed during incomplete polymerization, such as terminal -NH<sub>2</sub>, -NH groups and N-oxides, exhibit some basicity and thus, g-C<sub>3</sub>N<sub>4</sub> is suitable for adsorption and activation of CO<sub>2</sub> molecules.<sup>11</sup> In spite of having these advantages, the photocatalytic activity of g-C<sub>3</sub>N<sub>4</sub> is low because of limited light absorption until 450 nm in the visible region of the solar spectrum, high charge recombination rate, and low surface area.<sup>8</sup>

For efficient g-C<sub>3</sub>N<sub>4</sub> photocatalyst design, adsorption of CO<sub>2</sub>, visible light absorption, and charge carrier separation and transfer to carry out redox reactions are the key factors that need to be considered. Different strategies such as doping of cations or anions, composite formation with different semiconductors, tuning of the morphology, and loading of metal

<sup>a</sup> Department of Chemical Sciences, Tata Institute of Fundamental Research (TIFR), Mumbai, India

<sup>b</sup> Shell Technology Center, Bangalore, India. E-mail: vivekpol@tifr.res.in;  
Tel: (+91) 8452886556

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ma00809b>



nanoparticles have been adopted to modify the structural, electronic and optical properties of  $g\text{-C}_3\text{N}_4$ .<sup>8</sup> Among these, the doping of cations into the  $g\text{-C}_3\text{N}_4$  matrix offers several advantages, such as tuning the bandgap by creating impurity states and the generation of active sites for trapping of photoexcited electrons and holes.<sup>12</sup> Potassium-doped  $g\text{-C}_3\text{N}_4$  has been studied for photocatalytic hydrogen generation and dye degradation.<sup>13–17</sup> To the best of our knowledge,  $\text{CO}_2$  conversion was barely reported using potassium-doped  $g\text{-C}_3\text{N}_4$ .<sup>18,19</sup> Doping of potassium ions into the matrix of  $g\text{-C}_3\text{N}_4$  was found to be beneficial in extending absorption in the visible region and efficient separation of charge carriers.<sup>13–17</sup> It was also anticipated that the presence of an alkali metal ion like potassium would help in improving the  $\text{CO}_2$  adsorption capacity of  $g\text{-C}_3\text{N}_4$ .<sup>18,19</sup> Sun *et al.*<sup>19</sup> introduced an amino group and intercalated the potassium ion in  $g\text{-C}_3\text{N}_4$  by post-treatment of  $g\text{-C}_3\text{N}_4$  and KOH. They reported that the generation of the excess amino group improves  $\text{CO}_2$  adsorption and activation and the presence of intercalated potassium ions enhanced the separation and transfer of charge carriers. The methane and CO generation was found to be 5.6 and 5.4 times higher than that of  $g\text{-C}_3\text{N}_4$ , respectively. Recently, Wang *et al.* reported CO generation at the rate of  $8 \mu\text{mol g}^{-1} \text{h}^{-1}$  over (2.08 at%) potassium-doped  $g\text{-C}_3\text{N}_4$ .<sup>18</sup> Previously, we reported hydrogen generation using  $g\text{-C}_3\text{N}_4$  decorated over dendritic fibrous nanosilica (DFNS) and it was found to be seven times higher as compared to that of the pristine  $g\text{-C}_3\text{N}_4$ .<sup>20</sup> The improvement in activity was attributed to the visible light enhancement, efficient separation of charge carriers and high surface area.

In continuation of our work on DFNS-based catalytic systems,<sup>20–24</sup> in this work, we doped potassium ions within the framework of  $g\text{-C}_3\text{N}_4$  coated over DFNS to further improve the photocatalytic  $\text{CO}_2$  conversion. Melamine treated with KOH was used as a precursor for the synthesis of potassium-doped  $g\text{-C}_3\text{N}_4$ . This is the first time that we have reported the synthesis of potassium-doped  $g\text{-C}_3\text{N}_4$  coated over DFNS using a vacuum-sealed quartz tube. The amount of potassium ions was varied and the modifications in the optical, electronic and structural properties of  $g\text{-C}_3\text{N}_4$  were assessed by different characterization techniques. The catalysts were investigated for photocatalytic  $\text{CO}_2$  conversion under visible light illumination. The changes in the structure of  $g\text{-C}_3\text{N}_4$  brought by doping with potassium ion and the role of DFNS as the support were investigated and the impact of structural changes was correlated with the photocatalytic property of the sample. Preferential evolution of methane over hydrogen generation was observed using potassium-doped samples.

## Experimental

### Synthesis

Potassium hydroxide-treated melamine (K-melamine) was synthesized by dispersing potassium hydroxide (KOH) and melamine in distilled water. The solution was stirred for 2 h. The solvent was evaporated to dryness at  $80 \text{ }^\circ\text{C}$  in an oven. The amount of KOH varied from 3.2, 25.5 and 45.5 wt% of melamine.

K-melamine (250 mg) and DFNS (500 mg) were mixed well by grinding for 1 h. During grinding, ethanol was added after every 20 min to ensure homogeneous mixing. After grinding, the mixture was kept in an oven at  $80 \text{ }^\circ\text{C}$  for 12 h. The dried sample (86 mg) was transferred to a quartz tube and the tube was evacuated at 0.3–0.6 mbar overnight and then sealed under vacuum. The sealed tube was then heated in two steps, first at  $400 \text{ }^\circ\text{C}$  for 2 h and then at  $550 \text{ }^\circ\text{C}$  for 2 h at a heating rate of  $10 \text{ }^\circ\text{C min}^{-1}$ . After cooling down to room temperature, the tube was broken to obtain a powder catalyst. The detailed synthesis procedure is given in Fig. S1 (ESI<sup>†</sup>). The sample was washed with water four times to remove the impurities. The samples were referred to as K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3 for 3.2, 25.5 and 45.5 wt% of KOH used during synthesis. Pristine  $g\text{-C}_3\text{N}_4$  without DFNS and CN/DFNS without K doping were also synthesized as controls using the same protocol.

### Characterization

Scanning electron microscopy (SEM) was performed on a Zeiss ULTRA instrument. For sample preparation, powders were dispersed in ethanol with the assistance of sonication and a drop of solution was placed on an aluminum SEM grid. The X-ray diffraction (XRD) patterns were recorded using a Panalytical X'Pert Pro powder X-ray diffractometer using  $\text{Cu K}\alpha$  radiation. A fixed amount of sample and KBr were mixed to record the FTIR spectra of the samples using a JASCO FT/IR-4700 instrument. The thermal stability of the samples was evaluated by using thermogravimetric analysis (TGA, Mettler Toledo). TGA was carried out by heating the samples in an alumina pan at a heating rate of  $10 \text{ }^\circ\text{C min}^{-1}$  from  $30 \text{ }^\circ\text{C}$  to  $800 \text{ }^\circ\text{C}$  under an air atmosphere. UV-visible DRS spectra were recorded using a Jasco spectrophotometer (Jasco V-770). Lifetime measurements were carried out by using a femto/picosecond laser as the excitation source and employing the time-correlated single photon counting (TCSPC) technique. For fluorescence lifetime measurements, 1 ps pulses of 732 nm radiation from a Ti-sapphire femto/picosecond laser (Spectra-Physics, Mountain View, CA), pumped by a Nd:YLF laser (Millenia X, Spectra-Physics), were frequency-doubled to 396 nm by using a frequency doubler/triplet (GWU, Spectra-Physics). The fluorescence decay curves were obtained at a laser repetition rate of 4 MHz using a microchannel plate photomultiplier (model R2809u, Hamamatsu Corp.) coupled to a TCSPC setup. The instrument response function (IRF) at 396 nm was obtained using a dilute colloidal suspension of a dried non-dairy creamer. The full width at half-maximum (FWHM) of the IRF was 90 ps and the number of channels used was 1024. All the data were fitted with triexponential fitting. It gives three-lifetime values of  $\tau_1$ ,  $\tau_2$  and  $\tau_3$  corresponding to amplitudes,  $A_1$ ,  $A_2$  and  $A_3$ , respectively. Average lifetime ( $\tau_{\text{avg}}$ ) was determined by using the following equation:<sup>26</sup>

$$\tau_{\text{avg}} = \frac{A_1 \times \tau_1^2 + A_2 \times \tau_2^2 + A_3 \times \tau_3^2}{A_1 \times \tau_1 + A_2 \times \tau_2 + A_3 \times \tau_3} \quad (1)$$

The surface area was calculated by applying Brunauer–Emmett–Teller (BET) theory to  $\text{N}_2$  physisorption data, which was recorded using a Micromeritics Flex3 analyzer. Approximately 100 mg



of each sample was degassed at 120 °C for 12 h prior to N<sub>2</sub> sorption analysis. CO<sub>2</sub> adsorption of the catalyst was studied using a Micromeritics Flex3 analyzer at 25 °C.

The XPS analysis of the sample was done using monochromated Al-K $\alpha$  radiation (1486.6 eV) as an X-ray source. The carbon signal at 284.6 eV was used as an internal reference. Peak fitting of the spectra was performed using XPSPEAK 4.1 software. The relative positions of the valence band ( $E_{VB}$ ) and conduction band ( $E_{CB}$ ) against NHE were calculated from the XPS valence band spectra.<sup>27</sup>

$E_{VB}$  against NHE is estimated using the following equation:

$$E_{VB} = \Delta E - E_{vac} + W_s \quad (2)$$

where  $\Delta E$ ,  $E_{vac}$  and  $W_s$  are the difference between the Fermi level and the valence band maximum, the vacuum level (4.5 eV), and the work function of g-C<sub>3</sub>N<sub>4</sub> (4.0 eV), respectively.

$E_{CB}$  is estimated using the following equation:

$$E_{CB} = E_{VB} - E_G \quad (3)$$

where  $E_G$  is the bandgap value derived from the Tauc plot.

### Photocatalytic CO<sub>2</sub> conversion

Photocatalytic CO<sub>2</sub> conversion was carried out in a Pyrex photoreactor (volume 50 mL). 1 wt% Pt was deposited over the K-CN/DFNS sample by a chemical reduction method using NaBH<sub>4</sub> as a reducing agent. (1 wt%) Pt/K-CN/DFNS sample (15 mg) was mixed with a small amount of water to form a paste and spread over the flat bottom of the reactor, having an area of 2.5 cm<sup>2</sup>. Then the reactor was dried at 80 °C in an oven for 30 min. After this, CO<sub>2</sub> was passed through a water bubbler to bring a mixture of CO<sub>2</sub> and H<sub>2</sub>O vapor into the photoreactor for 1 h at a flow rate of 200 mL min<sup>-1</sup>. The reactor was irradiated with visible light (wavelengths 385–740 nm) using a 300 W xenon lamp (MAX 303 Asahi Spectra Co. Ltd). The output power of the lamp was adjusted to deliver 318 mW cm<sup>-2</sup> at the reactor. The photograph of the experimental setup is given in Fig. S2 (ESI<sup>†</sup>). Hydrogen and methane yields were monitored by gas chromatography (Agilent 7890B, Agilent Technologies) equipped with a thermal conductivity detector (TCD) and a flame ionization detector (FID). To compare the photocatalytic activity of the photocatalyst, the total consumed electron number (TCEN) was calculated. The methane generation requires 8 electrons. The formula used for the calculation of TCEN is as follows:

$$TCEN = \frac{\sum (C_{product} \times n_{electrons}) \times V_{reactor}}{m_{cat} \times t_{irr}} \quad (4)$$

$C_{product}$  is the concentration of the product,  $n_{electron}$  is the number of electrons involved in the conversion of CO<sub>2</sub> into methane,  $m_{cat}$  is the catalyst amount in g and  $t_{irr}$  is the time of irradiation in h.

To confirm that the hydrocarbon products are generated by the reduction of CO<sub>2</sub>, isotopically labeled experiments were carried out. For this experiment, <sup>13</sup>CO<sub>2</sub> was used as a reactant. The generated gaseous products after the reaction were analyzed by using GC coupled with mass spectrometry

(Agilent 7890B, Agilent Technologies). For GC-MS analysis, helium was used as the carrier gas and an Agilent hybrid column CP7430 as the stationary phase.

## Results and discussion

g-C<sub>3</sub>N<sub>4</sub> is a potential candidate for photocatalytic CO<sub>2</sub> conversion. However, low surface area, the high recombination rate of charge carriers and limited light absorption in the visible region affect its photocatalytic properties. In our previous publication, to overcome these issues, we coated g-C<sub>3</sub>N<sub>4</sub> over a high surface area support DFNS (CN/DFNS).<sup>20</sup> It showed seven times better hydrogen generation as compared to the pristine g-C<sub>3</sub>N<sub>4</sub>. The enhancement in photocatalytic activity was attributed to the high surface area, extended visible light absorption in the 450–650 nm range and improved charge separation due to the formation of an interface between DFNS and g-C<sub>3</sub>N<sub>4</sub>. The samples were further tested for CO<sub>2</sub> conversion. Unfortunately, it showed hydrogen as a major product and a low yield of methane. To improve its CO<sub>2</sub> conversion process, increase the selectivity towards CO<sub>2</sub> reduction products and suppress hydrogen generation, in this work, potassium ions were doped into the matrix of g-C<sub>3</sub>N<sub>4</sub> loaded over DFNS (K-CN/DFNS).

For the synthesis of K-CN/DFNS, KOH-treated melamine was mixed with DFNS and placed in a vacuum-sealed quartz tube and then heated at 400 °C for 2 h and 550 °C for 2 h. The amount of potassium was varied by changing the KOH amount from 3.2 to 45.5 wt% of melamine. The morphology of the samples was analyzed by SEM (Fig. 1). The SEM images of DFNS showed the presence of a fiber-like morphology with particle size in the range of 300–500 nm, whereas that of the CN/DFNS and K-CN/DFNS samples revealed that the layers of g-C<sub>3</sub>N<sub>4</sub> were grafted over the DFNS nanosheets, giving it a complete sphere-shape appearance (Fig. 1). The amount of potassium and g-C<sub>3</sub>N<sub>4</sub> content in the sample was evaluated using EDX analysis (Table 1). The amount of potassium varied from 0.74, 6.06 and 18.9 wt% with respect to g-C<sub>3</sub>N<sub>4</sub> for the K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3 samples, respectively. The content of g-C<sub>3</sub>N<sub>4</sub> was found to be lower in the case of K-CN/DFNS-3 as compared to the K-CN/DFNS-1 and K-CN/DFNS-2 samples.

To determine the structural modification after doping with potassium ions, the PXRD, FTIR and XPS analyses of the K-CN/DFNS samples were recorded. The PXRD pattern of g-C<sub>3</sub>N<sub>4</sub> (Fig. 2a) shows peaks at 13.2° and 27.9° corresponding to the 100 and 002 planes, which were ascribed to in-planar repeating units with a period of 0.672 nm and layered stacking with the interplanar spacing of 0.319 nm of aromatic systems, respectively.<sup>25,28</sup> K-CN/DFNS samples show a very small peak at 27.7° corresponding to the 002 plane of g-C<sub>3</sub>N<sub>4</sub>. The absence of other peaks at 13.2° corresponding to the 100 plane could be because of its lower content and the presence of overlapping broad peaks of amorphous SiO<sub>2</sub> at 22.7°.

To investigate the structural modification after doping with potassium ions, the FTIR spectra of the samples were recorded (Fig. 2b). The FTIR spectrum of g-C<sub>3</sub>N<sub>4</sub> shows absorption bands



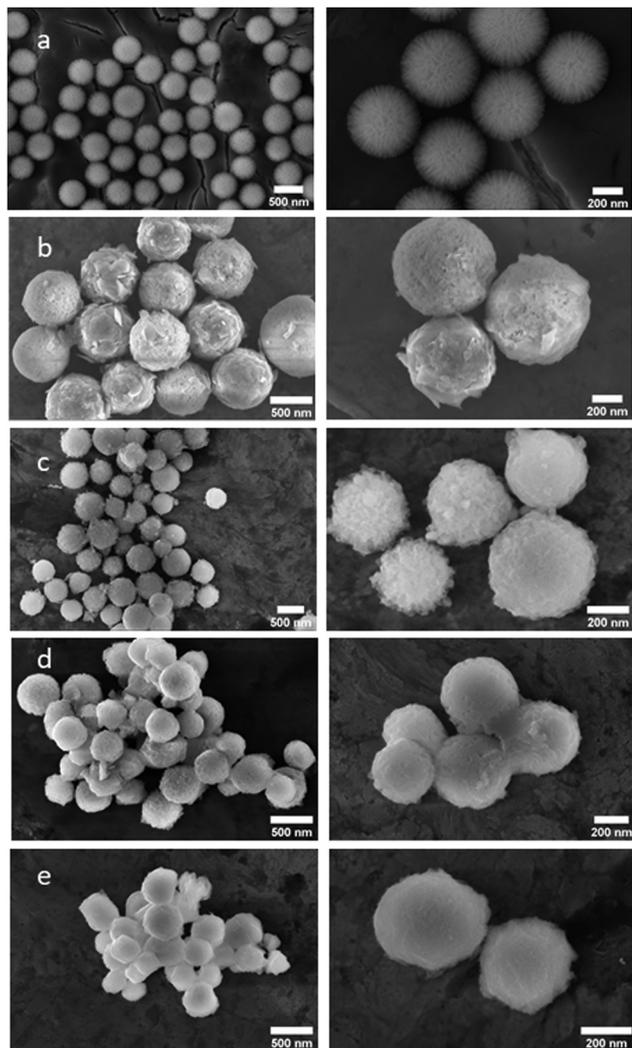


Fig. 1 The SEM images of the (a) DFNS, (b) CN/DFNS, (c) K-CN/DFNS-1, (d) K-CN/DFNS-2 and (e) K-CN/DFNS-3 samples (images from left to right indicate low resolution and high-resolution images).

at 810 and 890  $\text{cm}^{-1}$  corresponding to the breathing mode of heptazine rings and the deforming mode of NH groups, respectively.<sup>29</sup> The absorption bands observed in the range of 1200–1700  $\text{cm}^{-1}$  correspond to stretching modes of the CN heterocycle.<sup>29</sup> The absorption band at 1641  $\text{cm}^{-1}$  corresponds to the C=N stretching vibration mode. Also, the absorption

bands characteristic of aromatic C–N stretching were observed at 1247, 1326, 1432 and 1565  $\text{cm}^{-1}$ . The broad band in the range of 3000–4000  $\text{cm}^{-1}$  attributed to stretching modes of the terminal –NH<sub>2</sub> or –NH groups arises due to the presence of uncondensed amine groups and the adsorbed water molecules.<sup>18,29</sup> Also, a small absorption band is observed at 2145  $\text{cm}^{-1}$ , which might correspond to the C–N stretching mode of the C≡N (cyano) group. The FTIR spectrum of DFNS shows absorption bands at 1097 and 1192  $\text{cm}^{-1}$  corresponding to transverse optical (TO) and longitudinal optical (LO) modes of the asymmetric stretching of the Si–O–Si bond, respectively.<sup>30</sup> The weak absorption band at 966  $\text{cm}^{-1}$  is attributed to Si–OH or Si–O–stretching and the absorption band at 807  $\text{cm}^{-1}$  is due to Si–O–Si symmetric stretching.<sup>30,31</sup> The band around 1638  $\text{cm}^{-1}$  corresponds to bending vibrations of –OH and the broadband centered around 3400  $\text{cm}^{-1}$  belongs to –OH and the adsorbed H<sub>2</sub>O molecules.<sup>20,30</sup> The K-doped samples and undoped sample show the characteristic FTIR absorption bands of both DFNS and g-C<sub>3</sub>N<sub>4</sub>.

It is found that the peak at 2180  $\text{cm}^{-1}$  corresponds to the asymmetric stretching mode of the cyano group and increases with an increase in the potassium content from 1 to 6 wt%. The cyano group appears as a result of incomplete polymerization.<sup>32</sup> The excess KOH may prevent the polymerization of melamine, leading to defects in the K-doped samples. Also, the peak at 966  $\text{cm}^{-1}$  corresponding to the Si–OH stretching disappeared in the case of the K-CN/DFNS-2 and K-CN/DFNS-3 samples, which might be due to the C–N–Si linkages that formed between Si–OH and –NH<sub>2</sub> groups of g-C<sub>3</sub>N<sub>4</sub>, which was verified by the solid-state <sup>13</sup>C and <sup>1</sup>H NMR study in our previous publication.<sup>20</sup> In the case of K-CN/DFNS-3, the weak absorption band in the region of 1200–1700  $\text{cm}^{-1}$  does not appear prominently because of the lower loading of g-C<sub>3</sub>N<sub>4</sub>.

Furthermore, to learn more about the oxidation state of different elements and the interaction between potassium ions and g-C<sub>3</sub>N<sub>4</sub>, the XPS spectra of CN/DFNS, K-CN/DFNS-2 and K-CN/DFNS-2-used samples were analyzed. A survey scan of CN/DFNS shows the presence of C, N, O and Si on the surface, while K-CN/DFNS shows the existence of C, N, O, Si and K elements.

Fig. 2c shows a high-resolution spectrum of C 1s, which was deconvoluted into three peaks, namely 284.6, 286.9 and 287.9 eV, which could be assigned to the adventitious carbon, C–NH<sub>x</sub> species, and sp<sup>2</sup> hybridized carbon N=C(N)<sub>2</sub>, respectively.<sup>19</sup> An increase in the area of the peak at 287.9 eV indicates the higher amount sp<sup>2</sup> hybridized carbon N=C(N)<sub>2</sub> of g-C<sub>3</sub>N<sub>4</sub> in

Table 1 Potassium content by EDX analysis, g-C<sub>3</sub>N<sub>4</sub> content by TGA, bandgap measurement by UV-Visible DRS and surface area and pore volume by N<sub>2</sub> BET surface area analysis

Sample	Amount of potassium with respect to g-C <sub>3</sub> N <sub>4</sub> by EDX (wt%)	Amount of g-C <sub>3</sub> N <sub>4</sub> from TGA <sup>a</sup> (wt%)	Bandgap measurement by UV-Visible DRS (eV)	Surface area (m <sup>2</sup> g <sup>-1</sup> )	Pore volume (cm <sup>3</sup> g <sup>-1</sup> )
DFNS	—	—	—	622	0.719
g-C <sub>3</sub> N <sub>4</sub>	—	—	2.70	15	0.05
CN/DFNS	—	21.9	2.76	150	0.163
K-CN/DFNS-1	0.74	19.8	2.74	88	0.158
K-CN/DFNS-2	6.06	13.3	2.69	55	0.062
K-CN/DFNS-3	18.9	2.7	2.80	79	0.086

<sup>a</sup> Amount of g-C<sub>3</sub>N<sub>4</sub> calculated from the weight loss in the region of 220–670 °C in the thermogram.



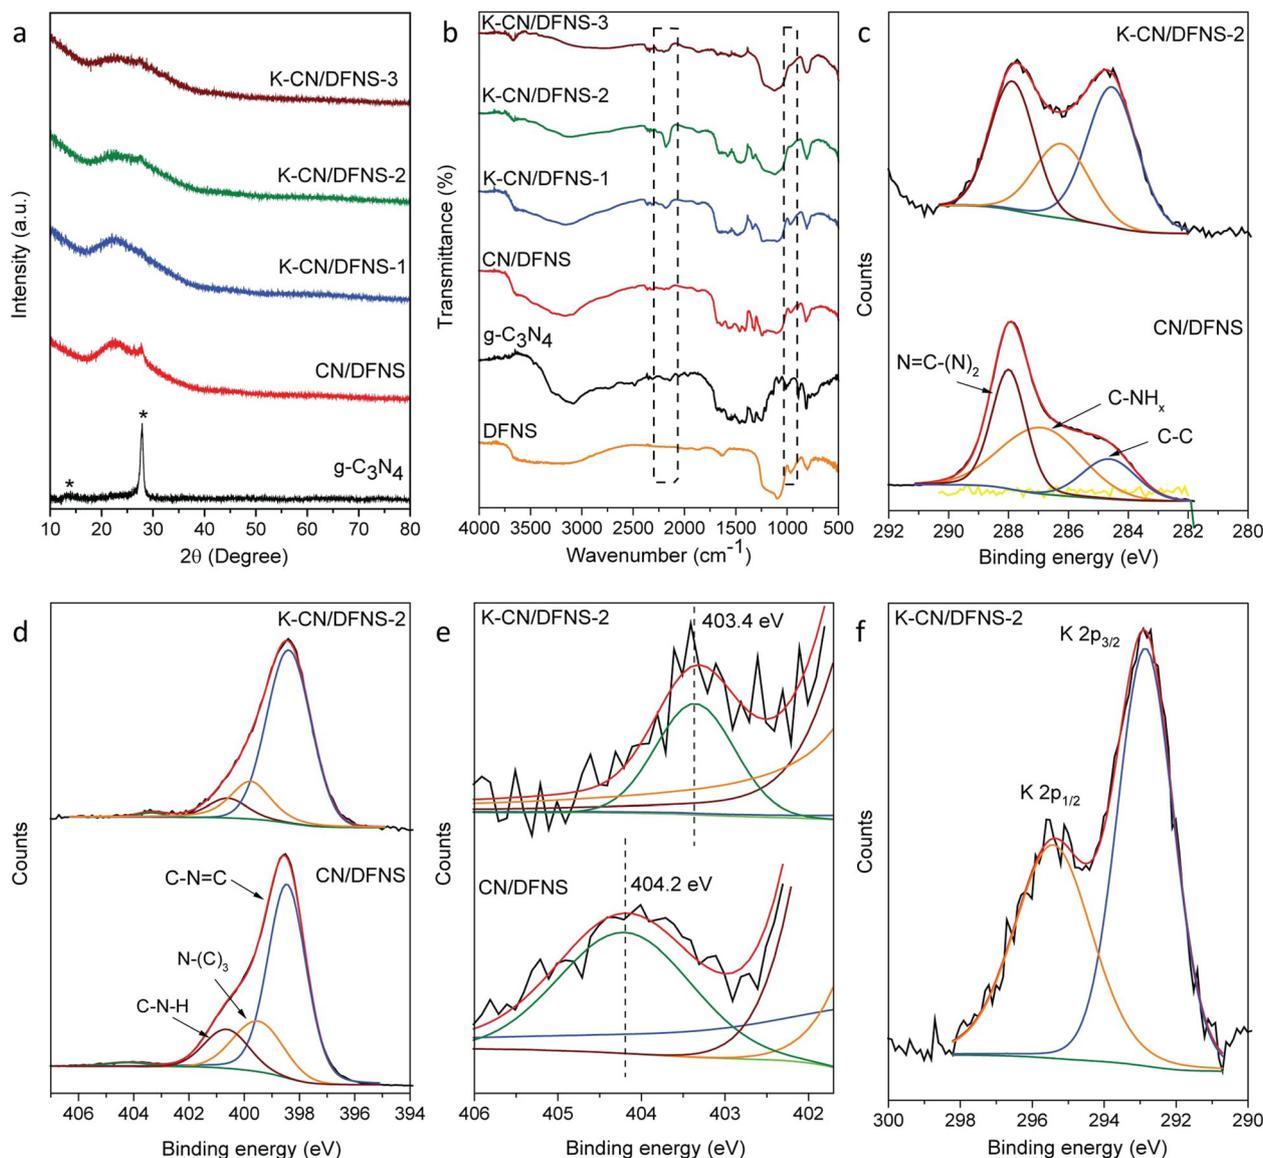


Fig. 2 (a) The XRD patterns and (b) FTIR spectra of DFNS,  $g\text{-C}_3\text{N}_4$ , CN/DFNS, K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3. The high-resolution XPS spectra of (c) C 1s and (d) N 1s, and (e) enlarged views of the peaks at 403 eV of N 1s and (f) K 2p of the CN/DFNS and K-CN/DFNS-2 samples (\* mark the planes of  $g\text{-C}_3\text{N}_4$ ).

CN/DFNS as compared to the K-CN/DFNS-2 sample. This can be correlated with the higher amount of  $g\text{-C}_3\text{N}_4$  in CN/DFNS than in the K-CN/DFNS-2 sample.

The high-resolution N 1s spectra of the samples were deconvoluted into four peaks (Fig. 2d). The peaks appeared at 398.5, 399.5, 400.6 and 404.2 eV. The peak at 398.5 eV corresponds to the  $sp^2$  N present in triazine rings, *i.e.* C–N=C bonds,<sup>19</sup> while the peaks at 399.5 and 400.6 eV correspond to the tertiary nitrogen group N–(C)<sub>3</sub> and amino group present due to incomplete polymerization, respectively.<sup>19</sup> The peak appearing at 404.2 eV is ascribed to the charging effect of  $\pi$  excitations of the C–N conjugated system.<sup>33</sup> The peak at 404.2 eV in CN/DFNS shifted to 403.4 eV in the potassium-doped  $g\text{-C}_3\text{N}_4$  sample (Fig. 2e). This indicates that the damage of the  $\pi$  electrons might be due to the disorder in the structure of  $g\text{-C}_3\text{N}_4$ .<sup>19</sup> Not much considerable shift

was observed with other types of nitrogen species present in the K-CN/DFNS sample.

Peaks at binding energy 292.8 and 295.4 eV in the K-CN/DFNS sample were assigned to K 2p<sub>3/2</sub> and K 2p<sub>1/2</sub>, respectively (Fig. 2f). These peaks could be due to the existence of K–N bonds.<sup>16</sup> Also, the presence of the K 2s peak at 377.8 eV confirms the existence of K–N bonds (Fig. S3a, ESI†).<sup>16,34</sup> The high-resolution O 1s spectrum shows peaks at positions of 532.6 and 533.7 eV originating from Si–O–Si bonds of silica and water molecules adsorbed on the surface, respectively (Fig. S3b, ESI†).<sup>23,35</sup> The peak at binding energy of 103.4 eV corresponds to the Si 2p of the siloxane framework of DFNS (Fig. S3c, ESI†).<sup>23</sup>

Thermogravimetric analysis of the sample was carried out to study the thermal stability of the material. TGA analysis from



30–800 °C in the presence of air was carried out (Fig. 3a). The thermogram of DFNS shows a weight loss in the region of 43–104 °C, corresponding to the loss of adsorbed water molecules. Pristine  $g\text{-C}_3\text{N}_4$  showed weight losses at 220–346 °C and 448–711 °C corresponding to the weight losses due to the decomposition of unreacted melamine or melam and decomposition of  $g\text{-C}_3\text{N}_4$ .<sup>36,37</sup> The thermogram of CN/DFNS showed weight losses in three steps. Step I: 34–132 °C corresponded to the weight loss due to physically adsorbed water. Step II: 132–283 °C was attributed to the weight loss due to the decomposition of residual intermediate products formed during the reaction. Step III: 310–670 °C was attributed to the thermal decomposition of  $g\text{-C}_3\text{N}_4$ .<sup>20</sup> The thermograms of the K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3 samples also show significant weight losses in two different regions. The weight loss occurred in two steps. Step I: 40–115 °C was attributed to the adsorbed water on the surface. Step II: 220–600 °C corresponded to the decomposition of  $g\text{-C}_3\text{N}_4$ . The offset temperature was found to

increase from 593 °C to 749 °C with the increase in the potassium content.

$\text{N}_2$  sorption analysis of K-CN/DFNS was performed to understand the textural properties and it showed a Type IV isotherm with hysteresis, indicating the mesoporous nature of the samples (Fig. S4 and S5, ESI†). The pores in the DFNS arise due to the gap between the fibres. CN/DFNS coated with 21.9 wt% of  $g\text{-C}_3\text{N}_4$  shows a surface area of  $150\text{ m}^2\text{ g}^{-1}$  lower than that of DFNS ( $622\text{ m}^2\text{ g}^{-1}$ ) but higher than  $g\text{-C}_3\text{N}_4$  ( $15\text{ m}^2\text{ g}^{-1}$ ). On the increase in the potassium content, the surface area varied from 88, 55 and  $79\text{ m}^2\text{ g}^{-1}$  for K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3, respectively (Table 1). The pore volumes of the samples change from 0.158, to 0.062 and  $0.086\text{ cm}^3\text{ g}^{-1}$  for K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3, respectively. The decrease in pore volume and surface area indicates the growth of  $g\text{-C}_3\text{N}_4$  on the DFNS fibers and also within the pores (channels) of the DFNS. The presence of potassium resulted in the distortion of the structure of  $g\text{-C}_3\text{N}_4$ , which could have resulted in a further

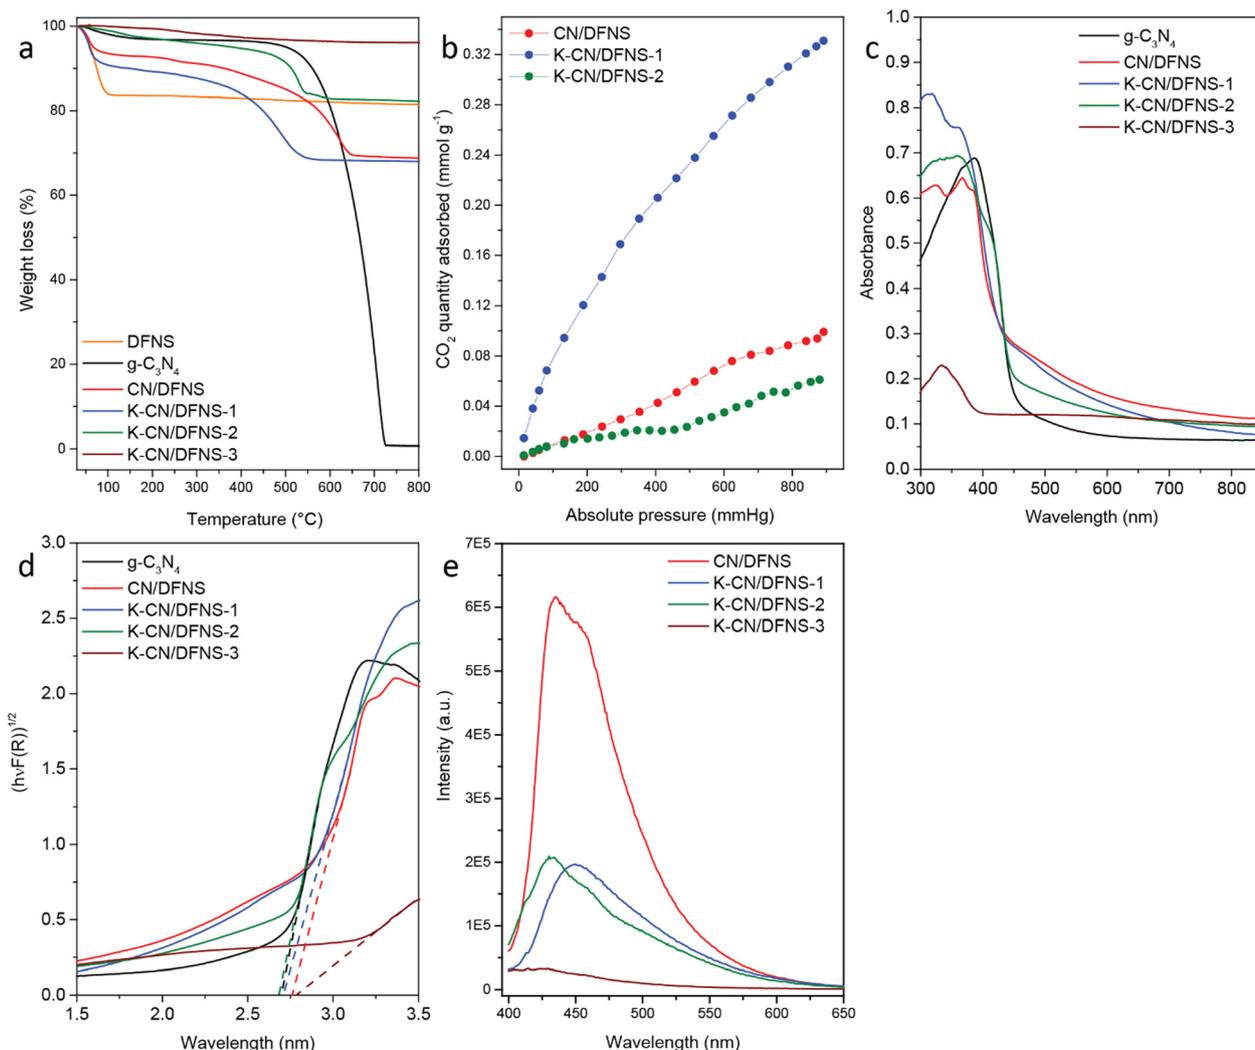


Fig. 3 (a) The TGA thermograms of the DFNS,  $g\text{-C}_3\text{N}_4$ , CN/DFNS and K-CN/DFNS samples, (b)  $\text{CO}_2$  adsorption over CN/DFNS, K-CN/DFNS-1 and K-CN/DFNS-2, (c) the DRS spectra, (d) the Tauc plots of  $g\text{-C}_3\text{N}_4$ , CN/DFNS and K-doped samples and (e) steady-state photoluminescence spectra of CN/DFNS and K-doped samples.



decrease in the pore size and surface area as compared to the undoped sample. Due to the lower loading of  $g\text{-C}_3\text{N}_4$  in K-CN/DFNS-3, a slight increase in surface area was observed.

$\text{CO}_2$  adsorption over different samples is given in Fig. 3b and Fig. S6 (ESI<sup>†</sup>). Among all the samples, K-CN/DFNS-1 has shown the highest  $\text{CO}_2$  adsorption of  $0.31 \text{ mmol g}^{-1}$  at 780 mm Hg of  $\text{CO}_2$  pressure and 298 K temperature. The improved adsorption could be due to increased basic sites in  $g\text{-C}_3\text{N}_4$ . These basic sites could be the increased  $-\text{NH}_2$  groups in the samples. K-CN/DFNS-2 is supposed to show higher  $\text{CO}_2$  adsorption as it has a higher content of potassium ions, around 6 wt%. However, it exhibits lower adsorption of  $\text{CO}_2$ . This could be due to the incomplete polymerization of  $g\text{-C}_3\text{N}_4$ , as evident from the presence of the cyano group, which might result in a decrease in the amino groups in the sample. The adsorption of  $\text{CO}_2$  in the cases of CN/DFNS and K-CN/DFNS-2 could be due to the presence of pyridinic nitrogen and terminal amino groups.

The optical properties of the samples were evaluated by recording the UV-Visible DRS absorption spectra of the samples (Fig. 3c). The bandgap of the samples was calculated using Tauc plots (Fig. 3d) and tabulated in Table 1. The bandgap of pristine  $g\text{-C}_3\text{N}_4$  was found to be 2.70 eV, while that of CN/DFNS was found to be 2.76 eV (Fig. 3c). CN/DFNS shows extended absorption in the range of 450–650 nm due to  $n \rightarrow \pi^*$  transition resulting from the distortion in the structure of  $g\text{-C}_3\text{N}_4$ .<sup>38</sup> This distortion could be due to the formation of C–N–Si linkages between DFNS and  $g\text{-C}_3\text{N}_4$  or the confined growth of  $g\text{-C}_3\text{N}_4$  within the pores of DFNS.<sup>20</sup> With the increase in the potassium content, the bandgap increases. The bandgap was found to be 2.71, 2.68 and 2.78 eV for K-CN/DFNS-1, K-CN/DFNS-2 and K-CN/DFNS-3, respectively. The bandgap value is found to be slightly lower for K-CN/DFNS-2. The lower content of  $g\text{-C}_3\text{N}_4$  in the case of K-CN/DFNS-3 resulted in the generation of thin sheets of  $g\text{-C}_3\text{N}_4$  grafted over DFNS. This might have resulted in the blueshift of the bandgap and less absorption of light. Along with the decrease in the bandgap on increasing the loading of potassium ions until 6 wt%, the absorption in the region of 450–650 nm increases. This absorption in the region of 450–650 nm occurs due to  $n \rightarrow \pi^*$  transition.<sup>38</sup> These  $n \rightarrow \pi^*$  transitions are forbidden in perfectly symmetric and planar units.<sup>17</sup> This transition becomes prominent with the increasing disorder in the structure of  $g\text{-C}_3\text{N}_4$ . In the case of doped samples, the presence of potassium ions inhibits the polymerization of  $g\text{-C}_3\text{N}_4$ , as evident from the presence of the cyano group in the FTIR spectra. This indicates that the presence of potassium ions not only affects the structural and thermal properties but also affects the electronic and optical properties of  $g\text{-C}_3\text{N}_4$ .

To gain insight into the separation of charge carriers, the steady-state and time-resolved photoluminescence spectra were recorded. The samples were excited at 380 nm and the emission spectra were recorded. Fig. 3e shows the steady-state photoluminescence spectra of the CN/DFNS and K-CN/DFNS samples. It was observed that the potassium-doped samples showed low emission intensity as compared to the CN/DFNS. This infers that the rate of radiative recombination of charges is low in the K-CN/DFNS samples as compared to CN/DFNS. K-CN/DFNS-3 (18.9 wt% potassium) showed the lowest emission intensity, while

its photocatalytic activity is low. CN/DFNS showed a broad emission peak centered at 434 nm, while in the case of the K-CN/DFNS samples, the emission peak was blue shifted. These results are in concurrence with the UV-Visible DRS spectra, where the bandgaps of the potassium-doped (6 wt% and 18.9 wt%) samples were found to be higher than that of CN/DFNS.

To further understand the lifetimes of charge carriers, time-resolved decay profiles were recorded. The samples were excited at 395 nm and decay profiles were recorded. The lifetime decay profile was fitted with the tri-exponential fitting decay eqn 1 (Table 2). In the case of doped samples, the average lifetimes were found to increase with an increase in the potassium amount. The contribution from the shortest lifetime ( $\tau_1$ ) increases with an increase in the potassium content. This indicates the effective transfer of charges to the impurity states or defect centers created after doping with potassium ions. This lowering in average lifetime as compared to  $g\text{-C}_3\text{N}_4$  might be due to the increased charge recombination by the non-radiative pathway. This was also evident from the lowering of the PL intensity in the steady-state experiments.

### Photocatalytic $\text{CO}_2$ conversion using K-CN/DFNS

Photocatalytic  $\text{CO}_2$  conversion of the samples was evaluated under visible light illumination (Fig. 4). Moist  $\text{CO}_2$  was passed over 15 mg of K-CN/DFNS/Pt (1 wt% Pt was pre-deposited by chemical reduction method) in a batch reactor for 1 h and then irradiated under a 300 W Xe lamp (384–750 nm,  $318 \text{ mW cm}^{-2}$ ). Quantification of  $\text{H}_2$  and  $\text{CH}_4$  generated after 4 h of reaction was monitored by GC-TCD-FID. CN/DFNS showed only hydrogen generation, whereas in the case of potassium-doped samples, no  $\text{H}_2$  generation was observed. The optimum amount of potassium content is needed to get the maximum photocatalytic activity. In this case, 6 wt% potassium-doped  $g\text{-C}_3\text{N}_4$  coated over DFNS shows the highest activity and preferential  $\text{CO}_2$  conversion over hydrogen generation. The highest methane yield observed was  $1.7 \mu\text{mol g}^{-1}$  of  $g\text{-C}_3\text{N}_4$  in 4 h using K-CN/DFNS-2 (6 wt% of potassium ion). The methane generation observed over the K-CN/DFNS-2 sample was found to be nearly three times higher than that of the pristine  $g\text{-C}_3\text{N}_4$ . The overall activity for methane generation was estimated from total consumed electrons using eqn (4) (TCEN). The TCEN for different samples were found to be 1.14, 0.64, and  $3.4 \mu\text{mol g}^{-1} \text{ h}^{-1}$  for the  $g\text{-C}_3\text{N}_4$ , K-CN/DFNS-1 and K-CN/DFNS-2, respectively. This enhancement in activity could be attributed to the improved light absorption, enhanced separation of charge carriers and suitable structural changes brought by the presence of the optimum amount of potassium.

Table 2 Lifetime measurements by time resolved photoluminescence

Sample name	$\tau_1$ (ns)	$A_1$	$\tau_2$ (ns)	$A_2$	$\tau_3$ (ns)	$A_3$	$\chi^2$	$\tau_{\text{avg}}$ (ns)
$g\text{-C}_3\text{N}_4$	0.841	0.406	2.509	0.484	7.445	0.11	1.08	3.97
CN/DFNS	0.525	0.581	1.909	0.354	6.927	0.064	1.02	3.17
K-CN/DFNS-1	0.122	0.791	1.271	0.166	5.27	0.043	1.694	1.45
K-CN/DFNS-2	0.048	0.895	0.821	0.08	4.236	0.025	2.926	2.35
K-CN/DFNS-3	0.018	0.92	0.988	0.061	4.929	0.02	1.004	3.11

Note: For all the samples excitation wavelength was 380 nm and emission wavelength was around 434 nm.



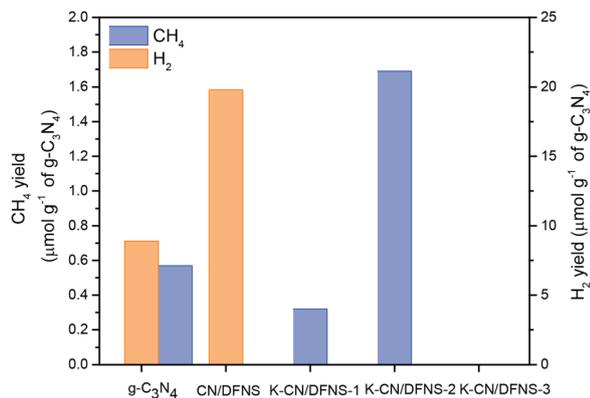


Fig. 4 Yields of CO<sub>2</sub> conversion products (methane) and hydrogen in 4 h using g-C<sub>3</sub>N<sub>4</sub>, CN/DFNS, and K-CN/DFNS samples in the presence of 1 wt% Pt as a cocatalyst under visible light illumination (385–740 nm).

On the contrary, despite having lower CO<sub>2</sub> adsorption, K-CN/DFNS-2 has shown better photocatalytic activity. CO<sub>2</sub> adsorption is not the only criterion that defines the better yield in photocatalytic CO<sub>2</sub> conversion. Other factors such as light absorption and the separation of charge carriers also play important roles. Therefore, in the case of K-CN/DFNS-2 the redshift in the absorption edge and the improved separation of charge carriers are the factors that influence the photocatalytic activity. In spite of having a greater average lifetime and extended absorption in the visible region, K-CN/DFNS-3 has not shown any conversion. This could be attributed to the lower amount of g-C<sub>3</sub>N<sub>4</sub> loading over DFNS and increased bandgap, which further obstruct the light absorption properties and thus result in the lower amount of charge carrier generation.

To confirm the source of the carbon, isotope-labeled experiments were performed using <sup>13</sup>C<sub>2</sub>O<sub>2</sub> and the products were analyzed by GC-MS. The mass fragmentation is given in Fig. S7 (ESI<sup>†</sup>).

A signal at  $m/z = 17$  corresponds to <sup>13</sup>CH<sub>4</sub>. This confirms that methane is generated from the reduction of CO<sub>2</sub>. In addition to this, the sample recovered after the CO<sub>2</sub> conversion reaction, K-CN/DFNS-2-used, was also studied by XPS (Fig. S8, ESI<sup>†</sup>). Not much change in the spectrum was observed. This implies that the catalyst remains stable after the photocatalytic reaction.

It is difficult to compare the yields of the products because of various experimental conditions such as intensity of the light source, amount of catalyst and water, reactor design, and distance between the reactor and light source. Very few reports are found on potassium-doped g-C<sub>3</sub>N<sub>4</sub> systems.<sup>18,19</sup> The methane yield reported in the current manuscript is lower than that in the reported literature on potassium-doped g-C<sub>3</sub>N<sub>4</sub> (Table S1, ESI<sup>†</sup>). However, the activity for CO<sub>2</sub> conversion using K-CN/DFNS was found to be higher than those of some of the doped g-C<sub>3</sub>N<sub>4</sub> systems reported in the literature.<sup>39–42</sup>

This is the first time that the role of DFNS as a support and the effects of various amount contents of potassium ion on the photocatalytic property of g-C<sub>3</sub>N<sub>4</sub> are studied. In this case, CN/DFNS, which showed a generation of primary hydrogen, was structurally modified by doping with potassium to tune the selectivity for CO<sub>2</sub> reduction. The structural changes brought by doping of potassium ions, such as generation of a cyano group, formation of K–N bonds and the interface between DFNS and g-C<sub>3</sub>N<sub>4</sub> through C–N–Si bonds, modification in the absorption spectrum and enhancement in charge carrier dynamics, have positively contributed to the improvement in activity and selectivity of the potassium-doped samples.

#### Band alignment and mechanism of photocatalytic CO<sub>2</sub> conversion

To understand the band structure and relative position of CB and VB, the valence band XPS spectra were recorded. The valence band XPS spectra of K-CN/DFNS-2 sample shows a

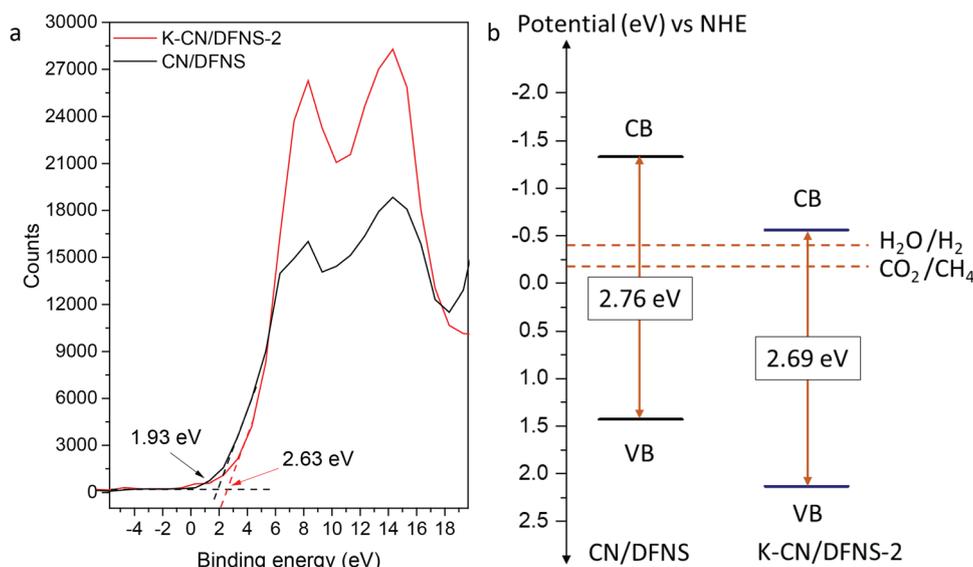




Fig. 5 (a) The valence band XPS spectra of CN/DFNS and K-CN/DFNS-2 and (b) energy diagram showing the positions of the conduction band (CB) and valence band (VB) of CN/DFNS and K-CN/DFNS-2 samples derived from the valence band XPS spectra and bandgap.



slight shift in the valence band edge as shown in Fig. 5a. The structural changes brought by the presence of potassium ions, such as the existence of a cyano group and the disordered structure of g-C<sub>3</sub>N<sub>4</sub> might have resulted in a shift in the position of the conduction and valence band edge.

From the valence band XPS spectra, the differences between the Fermi level and valence band maximum ( $\Delta E$ ) of CN/DFNS and K-CN/DFNS-2 were found to be 1.93 and 2.63 eV, respectively.  $E_{VB}$  was calculated using eqn (2). The valence band ( $E_{VB}$ ) of CN/DFNS and K-CN/DFNS-2 were found to be 1.43 and 2.13 eV, respectively. The conduction band ( $E_{CB}$ ) was calculated using the bandgap value estimated from  $E_{VB}$  and the Tauc plot (Table 1 and Fig. 3d). The  $E_{CB}$  values of CN/DFNS and K-CN/DFNS-2 were found to be  $-1.33$  and  $-0.56$  eV, respectively. Fig. 5b shows the positions of the conduction and valence bands in the CN/DFNS and K-CN/DFNS-2 samples.

The thermodynamic potential for the generation of methane and hydrogen are as follows:<sup>43</sup>



Due to the presence of potassium ions, both  $E_{CB}$  and  $E_{VB}$  of the K-CN/DFNS-2 samples have altered. The K-CN/DFNS-2 sample has a suitable band position for the generation of methane from CO<sub>2</sub> and reduction of water. The position of the CB is more negative than the standard reduction potential of CO<sub>2</sub>, thus making its photocatalytic reduction feasible.

Lowering the conduction band potential to vary the potential of photogenerated electrons is one of the strategies to tune the product selectivity.<sup>44</sup> In this case, the lowering of  $E_{CB}$  of the K-CN/DFNS-2 sample by  $-0.77$  eV as compared to that of CN/DFNS might be the reason for the improved selectivity for CO<sub>2</sub> conversion.

The following mechanism was predicted from the observed data: when light falls on K-CN/DFNS, an electron gets excited to the conduction band by leaving behind a hole. The photo-generated hole can oxidize water and release protons, while the electron can migrate to Pt, where it can reduce CO<sub>2</sub> in the presence of a proton to give methane. As compared to pristine g-C<sub>3</sub>N<sub>4</sub>, K-CN/DFNS-2 has shown better activity for methane generation and prohibited hydrogen generation due to the enhanced absorption of light, better separation of charge carriers, the shift of the conduction band and valence band towards positive potentials and moderate adsorption of CO<sub>2</sub>.

## Conclusions

In this work, we were able to tune the selectivity of K-CN/DFNS and preferentially reduce CO<sub>2</sub> over water reduction to generate hydrogen by simple potassium ion doping into the matrix of g-C<sub>3</sub>N<sub>4</sub>. It was observed that the potassium ion doping affected the structural, thermal, optical and electronic properties of g-C<sub>3</sub>N<sub>4</sub>. The SEM images confirm the grafting of the layers of potassium-doped g-C<sub>3</sub>N<sub>4</sub> over DFNS. The presence of potassium ions hampers the polymerization of g-C<sub>3</sub>N<sub>4</sub>, which was evident

from the presence of the cyano group in the FTIR spectra of the potassium-doped samples. The XPS analysis further confirms the interaction of potassium ions with the nitrogen of g-C<sub>3</sub>N<sub>4</sub> and the disordered structure of g-C<sub>3</sub>N<sub>4</sub>. The lowering of the bandgap and the extended absorption in visible light was observed until 6 wt% of potassium ion loading. Also, the lifetime of the charge carriers increases with an increase in the potassium content. Improved productivity for CO<sub>2</sub> conversion and suppression of hydrogen generation reaction was found over the potassium-doped samples. Among all the samples, K-CN/DFNS-2 (with 6 wt% of potassium ion doped in g-C<sub>3</sub>N<sub>4</sub>) has shown the highest CO<sub>2</sub> conversion, with a 1.7  $\mu\text{mol g}^{-1}$  of g-C<sub>3</sub>N<sub>4</sub> yield of methane, in 4 h under visible light irradiation. The UV-DRS, PL, and lifetime measurement studies indicated that the improved activity and preferential CO<sub>2</sub> reduction over hydrogen generation were due to the extended absorption in the visible region, better separation of charge carriers, shifting of the conduction band and valence band towards positive potentials and moderate adsorption of CO<sub>2</sub>. This study will be useful for the designing of catalysts with improved selectivity for CO<sub>2</sub> conversion over hydrogen generation.

## Conflicts of interest

There are no conflicts to declare.

## References

- M. Khalil, J. Gunlazuardi, T. A. Ivandini and A. Umar, Photocatalytic conversion of CO<sub>2</sub> using earth-abundant catalysts: A review on mechanism and catalytic performance, *Renewable Sustainable Energy Rev.*, 2019, **113**, 109246.
- L. Xu, Y. Xiu, F. Liu, Y. Liang and S. Wang, Research progress in conversion of CO<sub>2</sub> to valuable fuels, *Molecules*, 2020, **25**, 3653.
- T. Kong, Y. Jiang and Y. Xiong, Photocatalytic CO<sub>2</sub> conversion: What can we learn from conventional COx hydrogenation?, *Chem. Soc. Rev.*, 2020, **49**, 6579–6591.
- U. Ulmer, T. Dingle, P. N. Duchesne, R. H. Morris, A. Tavasoli, T. Wood and G. A. Ozin, Fundamentals and applications of photocatalytic CO<sub>2</sub> methanation, *Nat. Commun.*, 2019, **10**, 3169.
- Z. Bi, R. Guo, X. Hu, J. Wang, X. Chen and W. Pan, Research progress on photocatalytic reduction of CO<sub>2</sub> based on LDH materials, *Nanoscale*, 2022, **14**, 3367–3386.
- Y. Miao, R. Guo, J. Gu, Y. Liu, G. Wu, C. Duan and W. Pan, Oxygen vacancy-rich BiO<sub>2</sub>-x: Super-active co-catalyst on g-C<sub>3</sub>N<sub>4</sub> for efficient visible-light photocatalytic CO<sub>2</sub> reduction, *J. CO<sub>2</sub> Util.*, 2021, **44**, 101377.
- G. Dong, Y. Zhang, Q. Pan and J. Qiu, A fantastic graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) material: Electronic structure, photocatalytic and photoelectronic properties, *J. Photochem. Photobiol., C*, 2014, **20**, 33–50.
- G. Mamba and A. K. Mishra, Graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) nanocomposites: A new and exciting generation of visible light



- driven photocatalysts for environmental pollution remediation, *Appl. Catal., B*, 2016, **198**, 347–377.
- 9 X. Wang, K. Maeda, A. Thomas, K. Takanebe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, A metal-free polymeric photocatalyst for hydrogen production from water under visible light, *Nat. Mater.*, 2009, **8**, 76–80.
  - 10 D. J. Martin, K. Qiu, S. A. Shevlin, A. D. Handoko, X. Chen, Z. Guo and J. Tang, Highly efficient photocatalytic H<sub>2</sub> evolution from water using visible light and structure-controlled graphitic carbon nitride, *Angew. Chem., Int. Ed.*, 2014, **53**, 9240–9245.
  - 11 S. Samanta and R. Srivastava, Catalytic conversion of CO<sub>2</sub> to chemicals and fuels: the collective thermocatalytic/photocatalytic/electrocatalytic approach with graphitic carbon nitride, *Mater. Adv.*, 2020, **1**, 1506–1545.
  - 12 L. Jiang, X. Yuan, Y. Pan, J. Liang, G. Zeng, Z. Wu and H. Wang, Doping of graphitic carbon nitride for photocatalysis: A review, *Appl. Catal., B*, 2017, **217**, 388–406.
  - 13 Y. Wang, S. Zhao, Y. Zhang, J. Fang, Y. Zhou, S. Yuan, C. Zhang and W. Chen, One-pot synthesis of K-doped g-C<sub>3</sub>N<sub>4</sub> nanosheets with enhanced photocatalytic hydrogen production under visible-light irradiation, *Appl. Surf. Sci.*, 2018, **440**, 258–265.
  - 14 J. Ma, W. Zhou, X. Tan and T. Yu, Potassium ions intercalated into g-C<sub>3</sub>N<sub>4</sub>-modified TiO<sub>2</sub> nanobelts for the enhancement of photocatalytic hydrogen evolution activity under visible-light irradiation, *Nanotechnology*, 2018, **29**, 21.
  - 15 J. Jiang, S. Cao, C. Hu and C. Chen, A comparison study of alkali metal-doped g-C<sub>3</sub>N<sub>4</sub> for visible-light photocatalytic hydrogen evolution, *Chin. J. Catal.*, 2017, **38**, 1981–1989.
  - 16 S. Hu, F. Li, Z. Fan, F. Wang, Y. Zhao and Z. Lv, Band gap-tunable potassium doped graphitic carbon nitride with enhanced mineralization ability, *Dalton Trans.*, 2015, **44**, 1084–1092.
  - 17 H. Katsumata, K. Sakakibara, I. Tateishi, M. Furukawa and S. Kaneco, Structurally modified graphitic carbon nitride with highly photocatalytic activity in the presence of visible light, *Catal. Today*, 2020, **352**, 47–53.
  - 18 S. Wang, J. Zhan, K. Chen, A. Ali, L. Zeng, H. Zhao, W. Hu, L. Zhu and X. Xu, Potassium-doped g-C<sub>3</sub>N<sub>4</sub> achieving efficient visible-light-driven CO<sub>2</sub> reduction, *ACS Sustainable Chem. Eng.*, 2020, **8**(22), 8214–8222.
  - 19 Z. Sun, S. Wang, Q. Li, M. Lyu, T. Butburee, B. Luo, H. Wang, J. M. T. A. Fischer, C. Zhang, Z. Wu and L. Wang, Enriching CO<sub>2</sub> activation sites on graphitic carbon nitride with simultaneous introduction of electron-transfer promoters for superior photocatalytic CO<sub>2</sub>-to-fuel conversion, *Adv. Sustainable Syst.*, 2017, **1**, 1700003.
  - 20 S. A. Rawool, A. Samanta, T. G. Ajithkumar, Y. Kar and V. Polshettiwar, Photocatalytic hydrogen generation and CO<sub>2</sub> conversion using g-C<sub>3</sub>N<sub>4</sub> decorated dendritic fibrous nanosilica: role of interfaces between silica and g-C<sub>3</sub>N<sub>4</sub>, *ACS Appl. Energy Mater.*, 2020, **3**, 8150–8158.
  - 21 A. Maity, R. Belgamwar and V. Polshettiwar, Facile synthesis protocol to tune size, textural properties & fiber density of dendritic fibrous nanosilica (DFNS): applications in catalysis and CO<sub>2</sub> capture, *Nat. Protoc.*, 2019, **14**, 2177–2204.
  - 22 V. Polshettiwar, Dendritic Fibrous Nano-Silica (DFNS): Discovery, Synthesis, Formation Mechanism, Catalysis, and CO<sub>2</sub> Capture-Conversion, *Acc. Chem. Res.*, 2022, **55**, 1395–1410.
  - 23 A. K. Mishra, R. Belgamwar, R. Jana, A. Datta and V. Polshettiwar, Defects in nanosilica catalytically convert CO<sub>2</sub> to methane without any metal and ligand, *Proc. Natl. Acad. Sci. U. S. A.*, 2020, **117**, 6383–6390.
  - 24 A. Maity, S. Chaudhari, J. J. Titman and V. Polshettiwar, Nanosponges of acidic amorphous aluminosilicate for catalysis, plastic degradation and CO<sub>2</sub> to fuel conversion, *Nat. Commun.*, 2020, **11**, 3828.
  - 25 K. Li, F.-Y. Su and W.-D. Zhang, Modification of g-C<sub>3</sub>N<sub>4</sub> nanosheets by carbon quantum dots for highly efficient photocatalytic generation of hydrogen, *Appl. Surf. Sci.*, 2016, **375**, 110–117.
  - 26 *Principles of Fluorescence Spectroscopy*, ed., Lakowicz J. R., Springer, USA, 2006.
  - 27 J. Huang, G. Nie and Y. Ding, Metal-free enhanced photocatalytic activation of dioxygen by g-C<sub>3</sub>N<sub>4</sub> doped with abundant oxygen-containing functional groups for selective N-deethylation of Rhodamine B, *Catalysts*, 2020, **10**, 6.
  - 28 Y. Yuan, L. Zhang, J. Xing, M. I. B. Utama, X. Lu, K. Du, Y. Li, X. Hu, S. Wang, A. Genç, R. Dunin-borkowski, J. Arbiol and Q. Xiong, High-yield synthesis and optical properties of g-C<sub>3</sub>N<sub>4</sub>, *Nanoscale*, 2015, **7**, 12343–12350.
  - 29 L. Ge, F. Zuo, J. Liu, Q. Ma, C. Wang, D. Sun, L. Bartels and P. Feng, Synthesis and efficient visible light photocatalytic hydrogen evolution of polymeric g-C<sub>3</sub>N<sub>4</sub> Coupled with CdS quantum dots, *J. Phys. Chem. C*, 2012, **116**, 13708–13714.
  - 30 R. Singh, N. Bayal, A. Maity, D. J. Pradeep, J. Trébosc, P. K. Madhu, P. Lafon and V. Polshettiwar, Probing the interfaces in nanosilica-supported TiO<sub>2</sub> photocatalysts by solid-state NMR and in situ FTIR, *ChemNanoMat*, 2018, **4**, 1231–1239.
  - 31 B. Lin, C. Xue, X. Yan, G. Yang, G. Yang and B. Yan, Facile fabrication of novel SiO<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> core-shell nanosphere photocatalysts with enhanced visible light activity, *Appl. Surf. Sci.*, 2015, **357**, 346–355.
  - 32 M. Zhang, X. Bai, D. Liu, J. Wang and Y. Zhu, Enhanced catalytic activity of potassium-doped graphitic carbon nitride induced by lower valence position, *Appl. Catal., B*, 2015, **164**, 77–81.
  - 33 J. Yu, K. Wang, W. Xiao and B. Cheng, Photocatalytic reduction of CO<sub>2</sub> into hydrocarbon solar fuels over g-C<sub>3</sub>N<sub>4</sub>-Pt nanocomposite photocatalysts, *Phys. Chem. Chem. Phys.*, 2014, **16**, 11492–11501.
  - 34 J. Sharma, T. Gora, J. D. Rimstidt and R. Staley, X-Ray photoelectron spectra of the alkali azides, *Chem. Phys. Lett.*, 1972, **15**, 232.
  - 35 A. Thøgersen, J. H. Selj and E. S. Marstein, Oxidation effects on graded porous silicon anti-reflection coatings, *J. Electrochem. Soc.*, 2012, **159**(5), D276–D281.
  - 36 Y. Zhao, Z. Liu, W. Chu, L. Song, Z. Zhang, D. Yu, Y. Tian, S. Xie and L. Sun, Large-Scale synthesis of nitrogen-rich carbon nitride microfibers by using graphitic carbon nitride as precursor, *Adv. Mater.*, 2008, **20**, 1777–1781.



- 37 S. C. Yan, Z. S. Li and Z. G. Zou, Photodegradation performance of g-C<sub>3</sub>N<sub>4</sub> fabricated by directly heating melamine, *Langmuir*, 2009, **25**, 10397–10401.
- 38 M. K. Bhunia, S. Melissen, M. R. Parida, P. Sarawade, J. Basset, D. H. Anjum, O. F. Mohammed, P. Sautet, T. L. Bahers and K. Takanabe, Dendritic tip-on polytriazine-based carbon nitride photocatalyst with high hydrogen evolution activity, *Chem. Mater.*, 2015, **27**, 8237–8247.
- 39 Q. Huang, J. Yuab, S. Cao, C. Cui and B. Cheng, Efficient photocatalytic reduction of CO<sub>2</sub> by amine-functionalized g-C<sub>3</sub>N<sub>4</sub>, *Appl. Surf. Sci.*, 2015, **358**, 350–355.
- 40 K. Wang, Q. Li, B. Liu, B. Cheng, W. Ho and J. Yu, Sulfur-doped g-C<sub>3</sub>N<sub>4</sub> with enhanced photocatalytic CO<sub>2</sub>-reduction performance, *Appl. Catal., B*, 2015, **176–177**, 44–52.
- 41 X. Liu, P. Wang, H. Zhai, Q. Zhang, B. Huang, Z. Wang, Y. Liu, Y. Dai, X. Qin and X. Zhang, Synthesis of synergetic phosphorus and cyano groups (–C≡N) modified g-C<sub>3</sub>N<sub>4</sub> for enhanced photocatalytic H<sub>2</sub> production and CO<sub>2</sub> reduction under visible light irradiation, *Appl. Catal., B*, 2018, **232**, 521–530.
- 42 M. Arumugam, M. Tahir and P. Prasertthdam, Effect of nonmetals (B, O, P, and S) doped with porous g-C<sub>3</sub>N<sub>4</sub> for improved electron transfer towards photocatalytic CO<sub>2</sub> reduction with water into CH<sub>4</sub>, *Chemosphere*, 2022, **286(2)**, 131765.
- 43 J. Pan, X. Wu, L. Wang, G. Liu, G. Q. Lu and H.-M. Cheng, Synthesis of anatase TiO<sub>2</sub> rods with dominant reactive {010} facets for the photoreduction of CO<sub>2</sub> to CH<sub>4</sub> and use in dye-sensitized solar cells, *Chem. Commun.*, 2011, **47**, 8361–8363.
- 44 J. Fu, K. Jiang, X. Qiu, J. Yu and M. Liu, Product selectivity of photocatalytic CO<sub>2</sub> reduction reactions, *Mater. Today*, 2020, **32**, 222–243.

