






Cite this: *RSC Adv.*, 2022, 12, 1862

Selective and efficient catalytic and photocatalytic oxidation of diphenyl sulphide to sulfoxide and sulfone: the role of hydrogen peroxide and TiO₂ polymorph†

Paweł Mikrut,  Aneta Świąś, Marcin Kobielusz, * Lucjan Chmielarz 
and Wojciech Macyk *

In this paper, we describe the role of anatase and rutile crystal phases on diphenyl sulphide (Ph₂S) catalytic and photocatalytic oxidation. The highly selective and efficient synthesis of diphenyl sulfoxide (Ph₂SO) and diphenyl sulfone (Ph₂SO₂) at titanium dioxide was demonstrated. Ph₂S oxidation in the presence of hydrogen peroxide at anatase-TiO₂ can take place both as a catalytic and photocatalytic reaction, while at rutile-TiO₂ only photocatalytic oxidation is possible. The reaction at anatase leads mainly to Ph₂SO₂, whereas, in the presence of rutile a complete conversion to Ph₂SO is achieved after only 15 min (nearly 100% selectivity). Studies on the mechanistic details revealed a dual role of H₂O₂. It acts as a substrate in the reaction catalysed only by anatase, but it also plays a key role in alternative photocatalytic oxidation pathways. The presented study shows the applicability of photocatalysis in efficient and selective sulfoxide and sulfone production.

Received 15th November 2021
Accepted 24th December 2021

DOI: 10.1039/d1ra08364c

rsc.li/rsc-advances

Introduction

Conventional routes of synthesis of many important organic chemicals often require harsh operating conditions, such as high temperature and pressure. Moreover, sometimes the presence of toxic oxidation or reduction agents is required, far from the principles of green chemistry. The development of synthesis, which offers efficient organic compound production under mild reaction conditions, is highly desirable. Consequently, a photocatalytic organic synthesis, which utilizes economically sustainable and clean solar energy, has achieved tremendous attention in recent years.¹ However, photocatalysis has been mostly considered as a non-selective process, involving activation of small molecules to initiate a chemical reaction (especially in water). These types of photocatalytic reactions include mainly processes governed by reactive oxygen species such as oxidation of alcohols,² oxidation of aromatics^{3,4} or oxidation of side chains.^{5,6} Nevertheless, a carefully selected photocatalyst and synthesis conditions in a non-aqueous solvent can lead to highly selective photocatalytic fine product formation.

Oxidation of organic sulphides (diphenyl sulphide, dimethyl sulphide) is one of the most important processes in organic

chemistry. The organic sulfoxides and sulfones, which are the products of this reaction, were found to be very important substances for pharmacy, medicine, or substrates in drug synthesis. They can be used for the production of antibacterial, antifungal,⁷ antihypertensive agents,⁸ and vasodilators.⁹ Many catalytic systems, containing, *e.g.*, V, Re, Ti, Mo, Te, W, Se, Fe elements, have been studied in a sulphide to sulfoxide oxidation.^{10–14} Titanium dioxide is used as a catalyst due to its desired physicochemical properties, high chemical stability, low cost of production, and lack of toxicity. Additionally, TiO₂ doped with vanadium was found to be an active catalyst of Ph₂S oxidation giving nearly 100% conversion of Ph₂S with high selectivity to Ph₂SO₂.¹⁵ SiO₂-TiO₂ mesoporous xerogel catalyses oxidation to the final product, diphenyl sulfone, with the selectivity of 85%.¹⁶ Furthermore, it was confirmed that titanosilicate zeolites (*inter alia*, Ti-beta,¹⁷ Ti-MWW,¹⁸ Ti-FER, MTS-1 (ref. 19) and Ti-ITQ-6 (ref. 20)) present a good catalytic activity in this process. NaIO₄, trichloroisocyanuric acid, sodium perborate, KMnO₄, can be successfully applied as oxidizing agents.²¹ However, hydrogen peroxide, H₂O₂, seems to be the most suited oxidizer due to its low environmental impact (H₂O is the only side product), nontoxicity, and high content of active oxygen.^{22–24} Aromatic sulphides can also be transformed using photocatalysts such as wide bandgap oxide semiconductors (TiO₂, ZnO, *etc.*). Although, they undergo deep oxidation in the aqueous media, sulfoxides, and sulfones are the main reaction products in the presence of organic solvents.²⁵ To the best of our knowledge, the air is the most common source of oxygen in the

Faculty of Chemistry, Jagiellonian University, ul. Gronostajowa 2, 30-387 Kraków, Poland. E-mail: macyk@chemia.uj.edu.pl; kobielusz@chemia.uj.edu.pl

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d1ra08364c



photocatalytic transformation of sulphides described in the literature. In this system, even when selectivity is high, the concentration of the final product is rather low. However, we showed recently that hydrogen peroxide is a crucial oxidation agent in the photocatalytic oxidation of Ph_2S .²⁶ No Ph_2S conversion after 3 hours of the reaction in both catalytic and photocatalytic tests conducted in the absence of H_2O_2 over bare and doped TiO_2 materials (concentrations of Ph_2S oxidation products below the detection limit) was observed. Nevertheless, in the presence of hydrogen peroxide, the reaction can occur at P25 (anatase and rutile mixture) both on the catalytic and photocatalytic way, with significantly higher conversion of Ph_2S under irradiation compared to the dark process. In our previous paper, we studied the influence of TiO_2 modification (doping with vanadium, zinc, or tin) on the Ph_2S oxidation. We suggested that the crystal phase composition has a higher influence on both catalytic and photocatalytic activity than the surface metal modifications.²⁶ The goal of this work is to understand the difference between anatase and rutile in catalytic and photocatalytic Ph_2S oxidation, describe the role of particular reactive oxygen species in these reactions, and learn how to control the reaction selectivity to different products.

Experimental

Materials

Titanium dioxide materials containing anatase phase [Hombikat N100 (N100), Sachtleben Chemie; Tronox AK-1 (TRX_A)], and rutile [Tronox TR (TRX_R); (CR-EL), Ishihara Sangyo] were studied.

Crystal structure, morphology and phase composition

The phase compositions of materials were studied by the powder X-ray diffraction (XRD) using a Rigaku MiniFlex 600 X-ray diffractometer (Cu K_α radiation, 0.3 mm Ni filter) in 2θ range from 10 to 90° , at speed 3° min^{-1} and 0.05° step. The crystal size was calculated based on the Scherrer equation. To calculate the crystal size the most intense peaks were used, *i.e.*, (101) and (110) for anatase and rutile, respectively.

Materials morphology was examined by scanning electron microscopy (SEM) Tescan VEGA 3 with an LaB_6 emitter. The measurements were performed on a carbon sheet.

The specific surface area (SSA) of studied materials was determined from nitrogen adsorption-desorption isotherms at 77 K using a Quantachrome Autosorb iQ-MP-AG-AG instrument. The Brunauer-Emmett-Teller model was applied.

Studies on reaction conversion and product selectivity

Catalytic and photocatalytic oxidation of diphenyl sulphide (Ph_2S , 98%, Sigma Aldrich) to diphenyl sulfoxide (Ph_2SO , 96%, Sigma Aldrich) and sulfone (Ph_2SO_2 , 97%, Sigma Aldrich), in the presence of hydrogen peroxide (30%, Sigma Aldrich) was investigated. The reaction mixture consisted of 0.4 mmol dm^{-3} of diphenyl sulphide, 10 cm^3 of acetonitrile (99.9%, Sigma Aldrich) and 0.1 mmol dm^{-3} of bromobenzene ($\geq 99.5\%$, Sigma Aldrich) used as the internal standard. In a typical experiment,

5 mg of the tested material powder was sonicated for 2 min in 10 cm^3 of the reaction mixture, then 2 mmol dm^{-3} of 30% hydrogen peroxide was added (suspension concentration of 0.5 g dm^{-3}). The prepared suspension was placed in a round quartz cuvette (5 cm dia., 1 cm optical path) and irradiated for 3 hours with a xenon lamp (XBO-150, Instytut Fotonowy) equipped with $10 \text{ cm}^3 0.1 \text{ mol dm}^{-3}$ CuSO_4 aqueous solution filter and a 320 nm cut-off filter. To determine the apparent quantum efficiency the photon flux in the range of 300 to 400 nm was measured with the StellarNet spectroradiometer. In the case of the catalytic studies, the reaction tests were performed in the dark in order to avoid a light-assisted conversion of Ph_2S . The progress of the reactions was monitored by HPLC analysis of the reaction mixture using a mixture of acetonitrile/water in the volume ratio of 70 : 30 as the eluent. The samples of the reaction mixtures were filtered using a $0.22 \mu\text{m}$ nylon membrane filter and analysed by the PerkinElmer Flexar chromatograph equipped with the COL-Analytical C18 column ($150 \text{ mm} \times 4.6 \text{ mm i.d.}$, $5 \mu\text{m}$ pore size). The column was maintained at 25°C during the analysis and the UV detector was set at 254 nm.

Electrochemical measurements

The electrochemical measurements were carried out in a three-electrode system with Ag/Ag^+ electrode [AgNO_3 (10 mmol dm^{-3}) in 0.1 mol dm^{-3} Bu_4NClO_4 in acetonitrile], platinum wire, and carbon electrode as the reference, counter, and working electrodes, respectively. As the electrolyte 0.1 mol dm^{-3} LiClO_4 solution in acetonitrile was used. The potential of the reference electrode relative to the standard hydrogen electrode (SHE) was set at +0.62 V based on the cyclic voltammetry measurement for ferrocene (scan speed 10 mV s^{-1}) and the literature value for Fc^+/Fc couple. The electrode potential was controlled by an electrochemical analyser (Bio-Logic, SP-150). The cyclic voltammetry (CV) was collected at room temperature, with a scan rate of 60 mV s^{-1} , from -0.1 V to 2.0 V vs. Ag/Ag^+ .

Hydroxyl radicals generation

The hydroxyl radicals generation by studied materials was examined in the reaction of terephthalic acid (TA) hydroxylation. TiO_2 (0.5 g dm^{-3}) suspended in 16 cm^3 of the TA solution (Aldrich, 98%; $3 \times 10^{-3} \text{ mol dm}^{-3}$ dissolved in 0.01 mol dm^{-3} NaOH , $\text{pH} = 7.6$) was irradiated with a xenon lamp (XBO-150, Instytut Fotonowy). To avoid excitation of TA a 320 nm cut-off filter was used as well as a near infra-red and IR filter (10 cm optical path, 0.1 mol dm^{-3} solution of CuSO_4). Samples of 1.5 cm^3 were collected during irradiation, then centrifuged to separate the photocatalyst powder. In the reaction of non-fluorescent TA with hydroxyl radicals, hydroxyterephthalic acid (TAOH) is formed. TAOH was monitored by emission spectroscopy. TAOH shows a broad emission band at $\lambda_{\text{max}} = 425 \text{ nm}$ (when excited at $\lambda_{\text{exc}} = 315 \text{ nm}$). Moreover, TAOH generation in the presence of hydrogen peroxide (2 mmol dm^{-3}) was investigated.



Results and discussion

Morphology and phase composition

Materials in the form of white powders were used for the catalytic tests. Scanning electron microscopy revealed that anatase and rutile materials form aggregates in size *ca.* 1 μm and below 0.5 μm , respectively (Fig. 1). The crystal structure of the materials was confirmed using X-ray diffraction (XRD) (Fig. S1†). The crystal size of anatase and rutile materials is *ca.* 20 and 50 nm, respectively. In XRD of all samples only one polymorph is present, only CR-EL material contains a small admixture of anatase, up to 1%.²⁷ Porosimetry measurements showed that the anatase samples have a much higher specific surface area than the rutile materials (Table 1).

Ph_2SO_2 was the main product of the photocatalytic Ph_2S oxidation at anatase materials. In the case of N100 material 100% conversion of Ph_2S was achieved after 45 minutes of irradiation (Fig. 2a). In the case of the reaction conducted at TRX_A material, total Ph_2S oxidation was reached after 1 hour of irradiation (Fig. 2b). A slightly better selectivity to Ph_2SO_2 was observed in the case of N100 (100% after 90 minutes of irradiation) than for TRX_A material. Diphenyl sulphide oxidation at anatase materials in the dark was tested as well. The reaction progress was observed for both anatase samples. Additionally, the reaction products were not observed in the absence of TiO_2 in the reaction mixture, even when the mixture was heated to 40 °C. Nevertheless, after 3 hours of irradiation in the same reaction mixture (without TiO_2 , with H_2O_2) a slight conversion (*ca.* 7%) of Ph_2S to Ph_2SO as the final product took place (Fig. S2a†). We suggest that the residual oxidation of diphenyl sulphide is possible due to H_2O_2 photolysis, although 320 nm cut-off filter was used. The absorbance of the initial reaction mixture is negligible above 320 nm (Fig. S2b†), however, direct

Table 1 Phase, specific surface area, and crystal size of studied materials^a

Material	Phase	Specific surface area/ $\text{m}^2 \text{g}^{-1}$	Crystal size/nm ± 0.1
N100	Anatase	97 ± 2	18.1
TRX_A	Anatase	90 ± 2	17.3
TRX_R	Rutile	5.5 ± 0.1	48.2
CR-EL	Rutile	8 ± 0.1	46.9

^a (Photo)catalytic conversion of diphenyl sulphide in the presence of anatase and rutile.

photolysis of H_2O_2 initiated at any wavelength lower than 380 nm was reported by Cataldo.²⁸

These results clearly show that the oxidation of Ph_2S in the presence of anatase materials is possible both as catalytic and photocatalytic processes. However, a significantly higher conversion of Ph_2S for photocatalytic conditions compared to the dark processes was observed (Fig. S3a and b†). A similar positive effect of light was observed when Ph_2SO as a substrate was used (Fig. S10†). Both photocatalytic and catalytic oxidation of Ph_2S at anatase materials leads mainly to Ph_2SO_2 production with the selectivity of almost 100% after 3 h of tests (Fig. 2a, b and S3c, d†). Nevertheless, for both anatase materials, during the first hour more sulfoxide is formed upon irradiation than under purely catalytic conditions.

Results of photocatalytic oxidation of Ph_2S at rutile materials are depicted in Fig. 2c and d. Photocatalytic conversion of Ph_2S at rutile materials was significantly faster compared to both photocatalytic and catalytic conditions applied to anatase materials. The total conversion of Ph_2S was observed after 15 and 30 min of irradiation for TRX_R and CR-EL, respectively (Fig. 2c and d). Based on these data and the measured photon flux the apparent quantum efficiency of Ph_2S to Ph_2SO conversion within the first 15 min of irradiation was $\geq 2\%$. Oxidation of Ph_2S at rutile materials led to Ph_2SO as the main product. High selectivity to Ph_2SO at the beginning of the photocatalytic reaction was noticed (*ca.* 100%). During the reaction course the selectivity to Ph_2SO was decreasing, while the production of Ph_2SO_2 became the dominant process. However, upon further irradiation, the production of Ph_2SO increased again, hence diphenyl sulfoxide was the main product of the long term photocatalytic oxidation at rutile (Fig. 2c and d). Contrary to anatase, rutile induced no conversion in the absence of light, neither for Ph_2S nor Ph_2SO used as a substrate (Fig. S4 and S11a†).

Interestingly, the total concentration of analyzed reactants (Ph_2S , Ph_2SO , Ph_2SO_2) decreased by *ca.* 5% during the experiments with rutile material under illumination. Moreover, in the case of photocatalytic reaction over CR-EL material, at chromatograms the appearance of low amounts of a new compound, not detected for any other material described above was observed. To elucidate the role of H_2O_2 in this reaction a new portion of H_2O_2 was added after 90 min of irradiation (Fig. S5†). No increase of the selectivity to Ph_2SO_2 was observed. Furthermore, in our previous work we showed that after almost

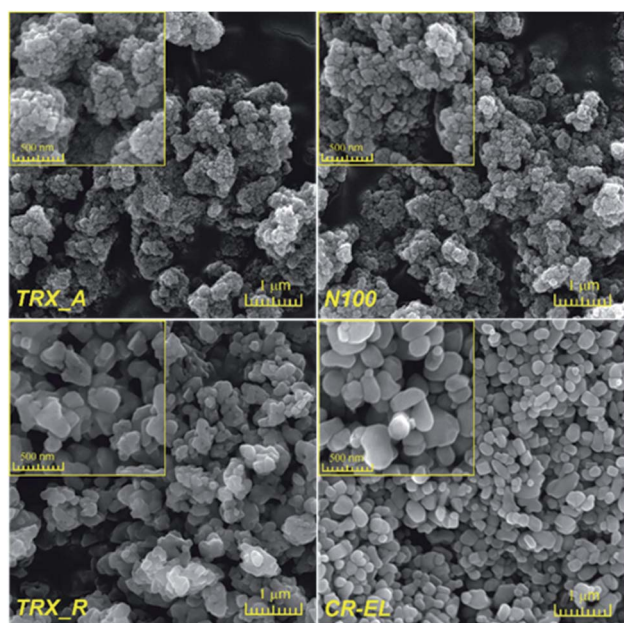


Fig. 1 SEM images of studied materials.



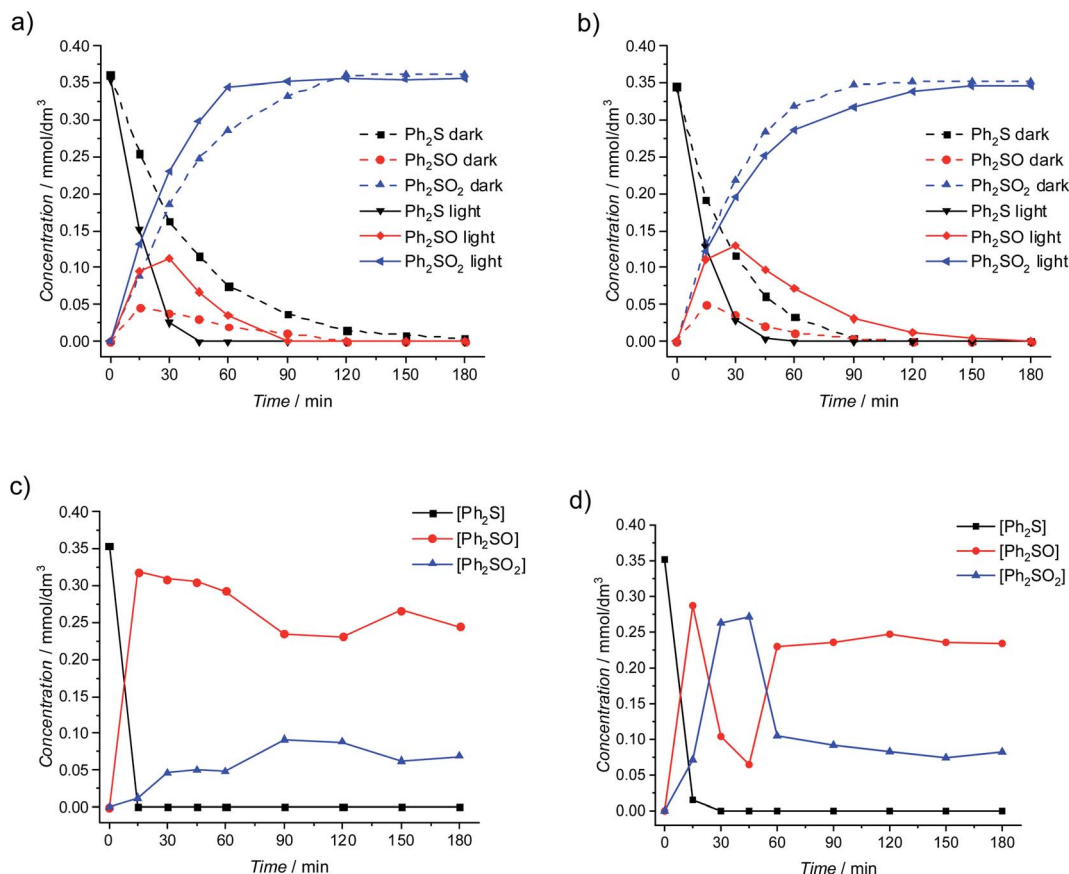


Fig. 2 Concentration of reactants during Ph_2S oxidation: at anatase materials (a) N100, (b) TRX_A upon irradiation $\lambda > 320$ nm (solid lines) and in the dark (dotted lines); at rutile material (c) TRX_R, (d) CR-EL upon irradiation.

complete conversion of Ph_2S into both Ph_2SO and Ph_2SO_2 , hydrogen peroxide was not totally consumed,²⁰ pointing at a sufficient amount of H_2O_2 used in the reaction. As the Ph_2SO_2 concentration decreases after prolonged irradiation (Fig. 2c), either its reduction to Ph_2SO or transformation to other products could be considered. A photocatalytic reduction of Ph_2SO_2 directly by electrons from the conduction band does not seem plausible, since 3 hours of irradiation of Ph_2SO_2 in the presence of H_2O_2 and CR-EL did not result in any Ph_2SO formation (data not shown). Moreover, the initial concentration of Ph_2SO_2 remained unchanged, what excludes a possibility of Ph_2SO_2 transformation to any other product. Taking these observations into account it was postulated that a decrease in Ph_2SO_2 and increase in Ph_2SO concentrations, observed after 45 min of the test, are possibly the result of Ph_2SO_2 disproportionation resulting a new unidentified compound. A detailed analysis of this product is still needed, however, we suggest that it could be one of many products identified by Vosoughian *et al.* in their meticulous analysis.²⁹

It is worth comparing the presented results with our earlier work where we tested the activity of doped titanium dioxide. Here we conclude, that rutile is not acting as a catalyst (*i.e.*, it is not active in the dark), however, we previously reported that materials with higher amounts of this polymorph show a higher activity in the oxidation of Ph_2S . Therefore, it can be concluded

that the presence of rutile has an indirect effect on the catalytic process – the material itself is not active, but the coexistence of rutile and anatase enhances the catalytic activity of the materials. Such anatase/rutile composites appeared also very active in photocatalytic transformations, both of Ph_2S and Ph_2SO , due to a synergistic effect of these phases reported in numerous publications on P25 and similar materials.^{30–34} N100 and TRX_A appear more active catalytically, therefore, in a similar time window the second oxidation product, Ph_2SO_2 , becomes the main product both in the dark and upon irradiation. The pure rutile phase, despite of its catalytic inactivity, appears the most active photomaterial. In this case a mixture of Ph_2SO and Ph_2SO_2 is obtained.

Reaction mechanism

Research studies on sulphides oxidation describe both catalytic and photocatalytic processes. The mechanism of catalytic oxidation involves H_2O_2 activation on the catalyst surface. Al-Maksoud *et al.* studied catalytic oxidation of various sulphides using H_2O_2 and self-synthesized TiO_2 (75–80% of anatase).²² The authors showed high selectivity to sulfones. Rodríguez-Padrón *et al.* studied microwave-assisted catalytic oxidation of sulphides using H_2O_2 and commercial anatase, as well as self-synthesized protein-templated anatase TiO_2 in



ethanol solution.³⁵ The authors showed that Ph₂S oxidation over reference anatase leads to sulfone production, while at protein-templated TiO₂ mainly sulfoxide was produced. Radko *et al.* studied catalytic oxidation of sulphides in the presence of titanosilicates and found that the dimethyl sulphide and diphenyl sulphide conversion increased with the increasing titanium content in the zeolite structure.²⁰ In our current study catalytic Ph₂S oxidation with H₂O₂ at anatase TiO₂ to Ph₂SO₂ was observed. Contrary to that, no catalytic oxidation of Ph₂S at rutile materials was observed. We suggest that the opposite results can be attributed to the various activation paths of hydrogen peroxide (and maybe Ph₂S) on the anatase/rutile surfaces. However, the differences can also originate from a low specific surface area of rutile materials, and therefore a low number of active sites. In order to elucidate the effect of specific surface area, the catalytic test with self-synthesized rutile material (SSA of ca. 25 m² g⁻¹) was performed. Although the specific surface area was 3–5 times higher in this case, no catalytic oxidation of Ph₂S was observed as well.

Published articles describing photocatalytic oxidation of sulphides postulate that the photocatalytic oxidation is initiated by the formation of a surface bound radical cation generated as a result of oxidation with the photogenerated hole.²⁹ Also, superoxide radical anion (O₂^{•-}) plays a key role in the reaction.^{36–38} Zhang *et al.* suggested that O₂^{•-} reacts with generated organosulfur radical.³⁹ Lang *et al.* studied Ph₂S visible light induced oxidation in the presence of a dye (alizarin red S) and TEMPO as the redox mediator to increase the dye stability.^{40–44} The authors reported Ph₂S conversion to Ph₂SO, pointing at O₂^{•-} importance in the reaction mechanism. Li *et al.* confirmed significance of superoxide radical anions and sulphide cation radicals by experiments involving radical scavengers and ¹⁸O₂.⁴⁵ Vosoughian *et al.* showed that oxidation of diphenyl sulphide was effective only in the oxygen rich atmosphere (detectable amounts of products were neither observed in the presence of atmospheric oxygen nor under argon flux).²⁹ In the presence of photosensitizers able to produce singlet oxygen, it is postulated that ¹O₂ may participate in the Ph₂S oxidation.^{46–49} The mechanism described in the literature (illustrated in Fig. 3, blue color) cannot fully explain our results, which show that no oxidation products are formed in the absence of hydrogen peroxide. In other words, the mechanism involving Ph₂S^{•+} formation and its reaction with either O₂^{•-} or ¹O₂ should lead to the products (Ph₂SO, Ph₂SO₂), which have not been detected.

According to our knowledge the role of H₂O₂ in the mechanism and its influence on the efficiency of photocatalytic Ph₂S oxidation have not been reported in the literature. The presence of H₂O₂ dramatically influences the generation of HO[•] and O₂^{•-}, both at rutile and anatase material (Fig. 3, red color). Photocatalytic production of hydroxyl radicals at rutile is inefficient, however, the generation of this reactive species is strongly enhanced in the presence of H₂O₂, as the result of its reduction. On the other hand, a similar effect of H₂O₂ on anatase photoactivity is not observed. Addition of H₂O₂ leads to increasing O₂^{•-} production at anatase, as the result of H₂O₂ oxidation with holes.⁵⁰ Generally, rutile has better reduction properties compared to anatase, meanwhile, anatase is a better

oxidant.³¹ Using various TiO₂ phase compositions in the combination with H₂O₂ can be an effective way to control the selectivity of the reaction in the system, in which a fine product formation is highly dependent on the generated ROS type. The HO[•] generation was monitored in the reaction of terephthalic acid oxidation. Hydroxyl radicals are generated as the result of a hole reaction with surface hydroxyl groups or adsorbed water molecules. In the reaction of TA with hydroxyl radicals, highly-fluorescent hydroxyterephthalic acid (TAOH) is formed. TAOH generation in the presence of hydrogen peroxide (2 mmol dm⁻³) was also investigated. The TAOH formation is depicted in Fig. S6.† In the absence of hydrogen peroxide anatase shows a more efficient HO[•] generation compared to the rutile (TAOH concentration amounted 57 μmol dm⁻³ and 29 μmol dm⁻³ respectively). However, after addition of H₂O₂ to the system containing anatase, TAOH generation decreased (10 μmol dm⁻³), while it significantly increased for rutile material (452 μmol dm⁻³). Undoubtedly, combination of hydrogen peroxide and rutile significantly enhances HO[•] generation.

The presence of hydrogen peroxide can lead to the increased concentration of photogenerated O₂^{•-} and/or HO[•] radicals, whereas only the influence of O₂^{•-} on the oxidation of Ph₂S is known. In order to determine the possible role of hydroxyl radicals in the reaction, the Fenton process was induced in the presence of Ph₂S. In the Fenton reaction (production of HO[•] in the reaction of H₂O₂ with iron(II) cations) the conversion of Ph₂S and efficient production of Ph₂SO were observed (Fig. 4a). Slight oxidation of Ph₂SO (Ph₂SO₂ formation) in the Fenton process was also noticed. However, an inefficient Ph₂SO₂ generation might originate from the transformation of other species that contaminate the original Ph₂SO sample (Fig. 4b). This shows that the hydroxyl radical and/or hydrogen peroxide (the reactant in this reaction) is able to oxidize Ph₂S to Ph₂SO. Recently, we described that the addition of *tert*-butyl alcohol (hydroxyl radical scavenger) significantly diminishes the Ph₂S conversion.²⁶ Furthermore, isotopic oxygen (H₂¹⁸O) experiments, reported by Li *et al.* revealed that the oxygen atoms of sulfoxide (obtained photocatalytically from phenyl sulphide in water containing mixture, in the absence of H₂O₂) originated mainly from water.⁵¹ We concluded that hydroxyl radicals play a significant role in the first step of diphenyl sulphide oxidation, yielding Ph₂SO. Similarly, in our actual system HO[•] is involved in the oxidation of Ph₂S to Ph₂SO, but the further oxidation to Ph₂SO₂ is not possible.

In order to explain why the Fenton reaction leads only to Ph₂SO generation, cyclic voltammetry measurements were performed (Fig. 5). In the case of Ph₂S, two oxidation peaks (*E*'_{a,Ph₂S} = 1.83 V vs. SHE; *E*'_{a,Ph₂S} = 2.07 V vs. SHE) and one reduction peak (*E*'_{c,Ph₂S} = 2.01 V vs. SHE) were observed in the cyclic voltammogram. In the case of Ph₂SO only one oxidation peak was detected (*E*'_{a,Ph₂SO} = 2.43 V vs. SHE). Finally, the CV of Ph₂SO₂ has shown neither oxidation nor reduction peaks in the explored potential range. In the case of Ph₂S cyclic voltammogram, the first oxidation at 1.83 V vs. SHE can presumably be attributed to Ph₂S^{•+} formation. Furthermore, based on the CV measurements the formation of Ph₂SO as an irreversible process was found. The second oxidation process at 2.07 V vs.



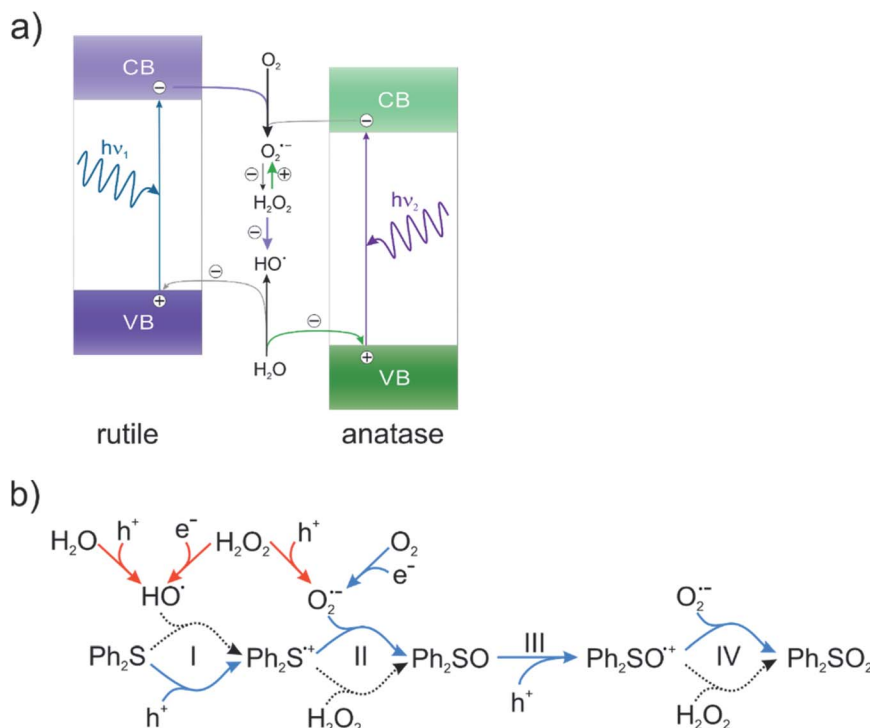


Fig. 3 (a) Main reactive oxygen species generation pathway in the presence of rutile and anatase photocatalysts, based on ref. 31. Violet and green arrows depict main processes characteristic for rutile and anatase, respectively. (b) Plausible pathway of Ph_2S oxidation at TiO_2 . Blue color shows the paths described in the literature so far. Red color shows pathways of H_2O_2 oxidation and reduction. Dotted black lines show discussed processes, which complete the mechanism of Ph_2S oxidation at TiO_2 in the presence of H_2O_2 .

SHE is a partially reversible reaction ($E'_{\text{c,Ph}_2\text{S}} = 2.01 \text{ V vs. SHE}$) with oxidation and reduction halfwaves separated by 0.06 V, pointing at one electron reversible process. Based on these considerations we conclude that oxidation of Ph_2S to Ph_2SO can be achieved by HO^\bullet ($\text{HO}^\bullet/\text{H}_2\text{O} = 2.27 \text{ V vs. SHE, pH} = 7$ (ref. 52)). CV of Ph_2SO reveals that the potential of sulfoxide oxidation is too high to enable its oxidation by hydroxyl radicals. Nevertheless, Ph_2SO can be still directly oxidized to $\text{Ph}_2\text{SO}^{\bullet+}$ by TiO_2 VB holes (step III, Fig. 3).⁵³

To summarize, the electrochemical and Fenton experiments showed that Ph_2S can be easily oxidized by HO^\bullet to $\text{Ph}_2\text{S}^{\bullet+}$. However, holes are required for further oxidation of Ph_2SO to the $\text{Ph}_2\text{SO}^{\bullet+}$ radical, which explains why the Fenton reaction led only to Ph_2SO . The Fenton process does not generate $\text{O}_2^{\bullet-}$, however, Ph_2SO as a product of the Fenton reaction was effortlessly detected. It is noteworthy that in the Fenton reaction the concentration of hydrogen peroxide was the same that in the photocatalytic system. The results suggest that H_2O_2 is involved in the $\text{Ph}_2\text{S}^{\bullet+}$ to Ph_2SO conversion (Fig. 3). Our

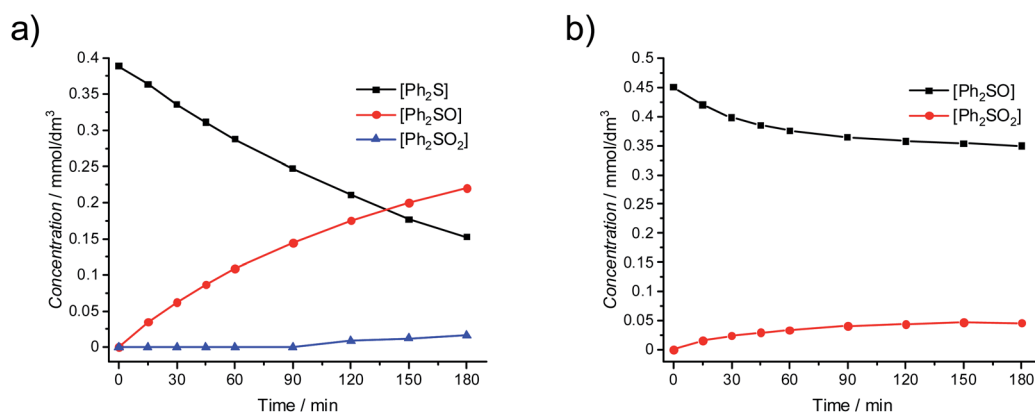


Fig. 4 Oxidation of (a) Ph_2S by the Fenton reagent ($0.4 \text{ mmol dm}^{-3} \text{ Ph}_2\text{S}$, $2 \text{ mmol dm}^{-3} \text{ H}_2\text{O}_2$, $0.2 \text{ mmol dm}^{-3} \text{ Fe}^{2+}$); (b) Ph_2SO by the Fenton reagent ($0.4 \text{ mmol dm}^{-3} \text{ Ph}_2\text{SO}$).



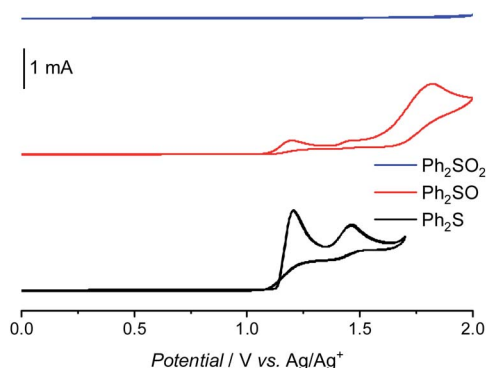


Fig. 5 Cyclic voltammograms of diphenyl sulphide, sulfoxide, and sulfone in acetonitrile.

hypothesized mechanism explains the results of photocatalytic oxidation of Ph_2S at anatase and rutile materials. In the case of rutile, a very fast conversion of Ph_2S was observed, due to a highly efficient H_2O_2 reduction, and thus effective HO^\bullet formation (Fig. S6†). These radicals oxidize Ph_2S within first few minutes of the reaction. Our study on HO^\bullet generation shows that in the presence of rutile and H_2O_2 ca. $400 \mu\text{mol dm}^{-3}$ of TAOH is generated after 15 min of irradiation (in aqueous solution). This concentration of hydroxyl radicals trapped as TAOH is equal to the initial concentration of Ph_2S in the tested reaction. These results clearly show that a fast conversion of Ph_2S at rutile CR-EL is a purely photocatalytic process, being a result of an efficient H_2O_2 reduction. At anatase, which preferably oxidizes H_2O_2 , HO^\bullet generation is much less effective, therefore, the oxidation rate is lower.

The presented results indicate that hydrogen peroxide and superoxide radical anion play a similar role, oxidizing the radical cations, $\text{Ph}_2\text{S}^{+\bullet}$ and $\text{Ph}_2\text{SO}^{+\bullet}$, to sulfoxide and sulfone, respectively. However, to unequivocally confirm these conclusions, the influence of oxygen on the reaction was tested. The studied reaction mixtures were purged with argon or oxygen before (15 min) and during the experiments. For the dark reaction at TRX_A, the observed conversion and selectivity were independent on the presence of oxygen (Fig. S7†). This result suggests that catalytic oxidation of Ph_2S involves only the activation of hydrogen peroxide activation, without any contribution of O_2 (alternatively, the contribution of oxygen is low, with a negligible influence on the products formation). However, when TRX_A was used as a photocatalyst (under irradiation), the influence of O_2 on the reaction progress was significant. A decrease of the Ph_2S conversion from ca. 60% under ambient conditions to ca. 35% under argon atmosphere and increased conversion to ca. 75% under the oxygen rich atmosphere was observed (Fig. S8a†). Under the oxygen free conditions, the Ph_2S conversion decreased, but photocatalytic oxidation of Ph_2S to Ph_2SO was still observed. Moreover, changes in the selectivity to Ph_2SO_2 at TRX_A were observed. The selectivity to Ph_2SO_2 increased in the following order: under argon, ambient, and oxygen-rich conditions (Fig. S8b†). In the case of the photocatalytic reaction at CR-EL, no significant changes in the Ph_2S conversion under various conditions were observed (Fig. S9a†).

Nevertheless, remarkable changes in the selectivity to Ph_2SO_2 were observed. Under oxygen-rich conditions a decrease in the production of Ph_2SO , and an increase in the Ph_2SO_2 production after first 15 min of the reaction, were observed (Fig. S9b†). Moreover, the point of the second increase of the Ph_2SO production appeared earlier (after 30 min of irradiation) for oxygen-rich conditions.

The first stable oxidation product, Ph_2SO , can be further oxidized by holes from the valence band of TiO_2 to $\text{Ph}_2\text{SO}^{+\bullet}$. This intermediate is further transformed to Ph_2SO_2 in the reaction with superoxide radical ($\text{O}_2^{\bullet-}$) formed as the result of either oxygen reduction or H_2O_2 oxidation. To confirm this path a possibility of Ph_2SO oxidation, both in the dark and upon irradiation in the presence of hydrogen peroxide and TiO_2 , was studied. In the case of anatase material, an efficient conversion of Ph_2SO to Ph_2SO_2 under both catalytic and photocatalytic conditions was observed, with a much better efficiency upon irradiation (Fig. S10†). In the case of rutile, no conversion was observed in the dark, however, irradiation induced this reaction (Fig. S11†). Clearly, the higher rate of the photocatalytic reaction in the case of anatase material is the result of a more efficient $\text{O}_2^{\bullet-}$ production at anatase than on the rutile in the presence of H_2O_2 . Furthermore, the possibility of Ph_2SO oxidation upon irradiation in the presence of TiO_2 , but in the absence of H_2O_2 , was tested (Fig. S12†). Low conversion of Ph_2SO under such conditions was observed – ca. 13% and 9% after 3 hours of irradiation in the presence of anatase and rutile, respectively. In a similar test, performed under anaerobic conditions (Ar-saturated solution and addition of Fe^{3+} as an electron acceptor), the conversion of Ph_2SO to Ph_2SO_2 was not observed. Abovementioned results clearly show that $\text{O}_2^{\bullet-}$ radicals can easily react with $\text{Ph}_2\text{SO}^{+\bullet}$, yielding Ph_2SO_2 . We suggest that the formation of Ph_2SO_2 is possible in the presence of $\text{O}_2^{\bullet-}$ and $\text{Ph}_2\text{SO}^{+\bullet}$ (hole oxidized Ph_2SO), however, such reaction has a low effectivity. In order to enhance the production of Ph_2SO_2 , the presence of hydrogen peroxide is necessary. The full mechanism of the photocatalytic Ph_2S oxidation in the presence of hydrogen peroxide is shown in Fig. 3.

Conclusions

In summary, we demonstrated that Ph_2S oxidation in the presence of hydrogen peroxide at anatase- TiO_2 can take place both as a catalytic and photocatalytic reaction. In contrast, at rutile materials only photocatalytic oxidation is possible, and no reaction progress was observed in the dark. The reaction at anatase leads mainly to Ph_2SO_2 as the product, whereas, the same reaction in the presence of rutile leads mainly to Ph_2SO formation. In the case of rutile the total conversion of Ph_2S was observed already after 15 min (compared to at least 1 h required for a catalytic conversion) with nearly 100% selectivity towards Ph_2SO . It is the first reported photocatalytic conversion of Ph_2S using H_2O_2 in the presence of pure rutile. Moreover, the efficiency of this reaction under the tested conditions is also much higher compared to the systems described in literature so far (apparent quantum yield of ca. 2%, concentration of products in the absence of H_2O_2 below the detection limit). The conversion



level and the reaction selectivity can be controlled by the choice between rutile and anatase polymorphs, as well as by irradiation time (in the case of rutile).

Catalytic oxidation of Ph₂S involves only the activation of hydrogen peroxide at the catalyst surface, without any contribution of dioxygen. Whereas, the presence of O₂ in the photocatalytic reaction increases the Ph₂S conversion due to generation of O₂^{•−}. Studies on the mechanistic details revealed the dual role of H₂O₂ (Fig. 3). At the same time, it plays the role of a substrate in the reaction catalysed only by anatase, but it also plays a key role in alternative oxidation pathways available through photocatalysis. Hydrogen peroxide can be either oxidized or reduced photocatalytically, resulting in the generation of O₂^{•−} and HO[•] radicals, respectively. Hydroxyl and superoxide radicals play an important role in various reaction steps. Hydroxyl radicals can oxidize Ph₂S to Ph₂S^{•+}, however, Ph₂SO oxidation to Ph₂SO^{•+} requires a stronger oxidant, *i.e.* holes. The cation radical intermediates, Ph₂S^{•+} and Ph₂SO^{•+}, react with superoxide anions or directly with H₂O₂ yielding stable sulfoxide (Ph₂SO) and sulfone (Ph₂SO₂).

The presented studies prove the applicability of photocatalysis in an efficient and selective synthesis of sulfoxide and sulfone through oxidation of organic sulphides.

Author contributions

Conceptualization P. M., M. K.; methodology P. M., M. K.; formal analysis P. M., M. K., A. Ś.; investigation P. M., M. K., A. Ś.; resources, L. C., W. M.; data curation P. M., M. K.; writing P. M., M. K., A. Ś., L. C. and W. M.; visualization P. M., M. K.; supervision M. K., W. M.; project administration W. M.; funding acquisition W. M.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The work on catalytic and photocatalytic properties of various TiO₂ polymorphs was supported by the Foundation for Polish Science (FNP) within the TEAM project (POIR.04.04.00-00-3D74/16). Selectivity and mechanistic studies were supported by the National Science Centre (NCN, Poland) within the Solar-Driven Chemistry project (2019/01/Y/ST5/00027).

References

- M. Kobielski, P. Mikrut and W. Macyk, in *Advances in Inorganic Chemistry*, Elsevier, 2018, vol. 72, pp. 93–144.
- T. Jedsukontorn, V. Meeyoo, N. Saito and M. Hunsom, *Chem. Eng. J.*, 2015, **281**, 252–264.
- T. D. Bui, A. Kimura, S. Ikeda and M. Matsumura, *J. Am. Chem. Soc.*, 2010, **132**, 8453–8458.
- F. F. Karam, M. I. Kadhim and A. F. Alkaim, *Int. J. Chem. Sci.*, 2015, **13**, 650–660.
- V. Augugliaro, G. Camera-Roda, V. Loddo, G. Palmisano, L. Palmisano, F. Parrino and M. A. Puma, *Appl. Catal. B Environ.*, 2012, **111**, 555–561.
- K. Schoumacker, C. Geantet, M. Lacroix, E. Puzenat, C. Guillard and J.-M. Herrmann, *J. Photochem. Photobiol. A*, 2002, **152**, 147–153.
- M. Sovova and P. Sova, *Ceska Slov. Farm.*, 2003, **52**, 82–87.
- B. Kotelanski, R. J. Grozmann and J. N. Cohn, *Clin. Pharmacol. Ther.*, 1973, **14**, 427–433.
- S. Padmanabhan, R. C. Lavin and G. J. Durant, *Tetrahedron: Asymmetry*, 2000, **11**, 3455–3457.
- K. Kaczorowska, Z. Kolarska, K. Mitka and P. Kowalski, *Tetrahedron*, 2005, **35**, 8315–8327.
- A. Mahdian, M. H. Ardakani, E. Heydari-Bafrooei and S. Saeednia, *Appl. Organomet. Chem.*, 2021, **35**, e6170.
- S. Mirfakhraei, M. Hekmati, F. H. Eshbala and H. Veisi, *New J. Chem.*, 2018, **42**, 1757–1761.
- W.-Y. Zhou, M. Chen, P.-Z. Zhang, A.-Q. Jia and Q.-F. Zhang, *Russ. J. Org. Chem.*, 2021, **57**, 816–824.
- J. Přech, R. E. Morris and J. Čejka, *Catal. Sci. Technol.*, 2016, **6**, 2775–2786.
- M. Radko, A. Kowalczyk, E. Bidzińska, S. Witkowski, S. Górecka, D. Wierzbicki, K. Pamin and L. Chmielarz, *J. Therm. Anal. Calorim.*, 2018, **132**, 1471–1480.
- A. M. Cojocariu, P. H. Mutin, E. Dumitriu, A. Aboulaich, A. Vioux, F. Fajula and V. Hulea, *Catal. Today*, 2010, **157**, 270–274.
- I. Martausová, D. Spustová, D. Cvejn, A. Martaus, Z. Lacný and J. Přech, *Catal. Today*, 2019, **324**, 144–153.
- Y. Kon, T. Yokoi, M. Yoshioka, Y. Uesaka, H. Kujira, K. Sato and T. Tatsumi, *Tetrahedron Lett.*, 2013, **54**, 4918–4921.
- Z. Kang, G. Fang, Q. Ke, J. Hu and T. Tang, *ChemCatChem*, 2013, **5**, 2191–2194.
- M. Radko, M. Rutkowska, A. Kowalczyk, P. Mikrut, A. Świąt, U. Díaz, A. E. Palomares, W. Macyk and L. Chmielarz, *Microporous Mesoporous Mater.*, 2020, 110219.
- M. B. Smith and J. March, *March's Advanced Organic Chemistry: Reactions, Mechanisms, and Structure*, 5th edn, Wiley, 2001.
- W. Al-Maksoud, S. Daniele and A. B. Sorokin, *Green Chem.*, 2008, **10**, 447–451.
- K. Sato, M. Hyodo, M. Aoki, X.-Q. Zheng and R. Noyori, *Tetrahedron*, 2001, **57**, 2469–2476.
- V. Hulea, F. Fajula and J. Bousquet, *J. Catal.*, 2001, **198**, 179–186.
- A. V. Vorontsov and P. G. Smirniotis, in *Environmentally Benign Photocatalysts: Applications of Titanium Oxide-based Materials*, ed. M. Anpo and P. V. Kamat, Springer New York, New York, NY, 2010, pp. 579–621.
- M. Radko, A. Kowalczyk, P. Mikrut, S. Witkowski, W. Mozgawa, W. Macyk and L. Chmielarz, *RSC Adv.*, 2020, **10**, 4023–4031.
- M. Kobielski, A. Nitta, W. Macyk and B. Ohtani, *J. Phys. Chem. Lett.*, 2021, **12**, 3019–3025.
- F. Cataldo, *Front. Chem.*, 2014, **23**, 99.
- H. Vosoughian and M. H. Habibi, *Int. J. Photoenergy*, 2007, **2007**, 7.



- 30 K. Yaemsunthorn, M. Kobielski and W. Macyk, *ACS Appl. Nano Mater.*, 2021, **4**, 633–643.
- 31 M. Buchalska, M. Kobielski, A. Matuszek, M. Pacia, S. Wojtyła and W. Macyk, *ACS Catal.*, 2015, **5**, 7424–7431.
- 32 B. Ohtani, O. Prieto-Mahaney, D. Li and R. Abe, *J. Photochem. Photobiol. Chem.*, 2010, **216**, 179–182.
- 33 H. Cheng, J. Wang, Y. Zhao and X. Han, *RSC Adv.*, 2014, **4**, 47031–47038.
- 34 K. Connelly, A. Wahab and H. Idriss, *Mater. Renew. Sustain. Energy*, 2012, **1**, 3.
- 35 D. Rodríguez-Padrón, A. R. Puente-Santiago, F. Luna-Lama, A. I. Caballero, M. J. Muñoz-Batista and R. Luque, *ACS Sustain. Chem. Eng.*, 2019, **7**, 5329–5337.
- 36 W. Sheng, J.-L. Shi, H. Hao, X. Li and X. Lang, *J. Colloid Interface Sci.*, 2020, **565**, 614–622.
- 37 H. Hao, X. Li and X. Lang, *Appl. Catal. B Environ.*, 2019, **259**, 118038.
- 38 J.-L. Shi and X. Lang, *Chem. Eng. J.*, 2020, **392**, 123632.
- 39 P. Zhang, Y. Wang, H. Li and M. Antonietti, *Green Chem.*, 2012, **14**, 1904–1908.
- 40 X. Lang, W. Hao, W. R. Leow, S. Li, J. Zhao and X. Chen, *Chem. Sci.*, 2015, **6**, 5000–5005.
- 41 X. Lang, J. Zhao and X. Chen, *Angew. Chem.*, 2016, **128**, 4775–4778.
- 42 H. Hao, Z. Wang, J. L. Shi, X. Li and X. Lang, *ChemCatChem*, 2018, **10**, 4545–4554.
- 43 X. Ma and X. Lang, *Sustain. Energy Fuels*, 2020, **4**, 1754–1763.
- 44 H. Hao, X. Li and X. Lang, *Appl. Catal. B Environ.*, 2019, **259**, 118038.
- 45 C. Li, N. Mizuno, K. Murata, K. Ishii, T. Suenobu, K. Yamaguchi and K. Suzuki, *Green Chem.*, 2020, **22**, 3896–3905.
- 46 H. Wang, S. Jiang, S. Chen, D. Li, X. Zhang, W. Shao, X. Sun, J. Xie, Z. Zhao and Q. Zhang, *Adv. Mater.*, 2016, **28**, 6940–6945.
- 47 J. Li, Y. Chen, X. Yang, S. Gao and R. Cao, *J. Catal.*, 2020, **381**, 579–589.
- 48 Q. Li, X. Lan, G. An, L. Ricardez-Sandoval, Z. Wang and G. Bai, *ACS Catal.*, 2020, **10**, 6664–6675.
- 49 R. S. Davidson and J. E. Pratt, *Tetrahedron Lett.*, 1983, **24**, 5903–5906.
- 50 T. Hirakawa, K. Yawata and Y. Nosaka, *Appl. Catal. Gen.*, 2007, **325**, 105–111.
- 51 B. Zhang, J. Li, B. Zhang, R. Chong, R. Li, B. Yuan, S.-M. Lu and C. Li, *J. Catal.*, 2015, **332**, 95–100.
- 52 M. Kaneko and I. Okura, *Photocatalysis: science and technology*, Springer, 2002.
- 53 C. Maheu, L. Cardenas, E. Puzenat, P. Afanasiev and C. Geantet, *Phys. Chem. Chem. Phys.*, 2018, **20**, 25629–25637.

