


 Cite this: *RSC Adv.*, 2022, 12, 8385

# Selective CO<sub>2</sub> adsorption and bathochromic shift in a phosphocholine-based lipid and conjugated polymer assembly†

 Juran Noh,<sup>a</sup> Dong Geon Koo,<sup>b</sup> Chohee Hyun,<sup>c</sup> Dabin Lee,<sup>b</sup> Seohyeon Jang,<sup>b</sup> Jiho Kim,<sup>e</sup> Yejee Jeon,<sup>b</sup> Su-Young Moon,<sup>d</sup> Boknam Chae,<sup>e</sup> Inho Nam,<sup>b</sup> Tae Joo Shin<sup>\*cf</sup> and Juhyun Park<sup>id \*b</sup>

We assemble a film of a phosphocholine-based lipid and a crystalline conjugated polymer using hydrophobic interactions between the alkyl tails of the lipid and alkyl side chains of the polymer, and demonstrated its selective gas adsorption properties and the polymer's improved light absorption properties. We show that a strong attractive interaction between the polar lipid heads and CO<sub>2</sub> was responsible for 6 times more CO<sub>2</sub> being adsorbed onto the assembly than N<sub>2</sub>, and that with repeated CO<sub>2</sub> adsorption and vacuuming procedures, the assembly structures of the lipid-polymer assembly were irreversibly changed, as demonstrated by *in situ* grazing-incidence X-ray diffraction during the gas adsorption and desorption. Despite the disruption of the lipid structure caused by adsorbed polar gas molecules on polar head groups, gas adsorption could promote orderly alkyl chain packing by inducing compressive strain, resulting in enhanced electron delocalization of conjugated backbones and bathochromic light absorption. The findings suggest that merging the structures of the crystalline functional polymer and lipid bilayer is a viable option for solar energy-converting systems that use conjugated polymers as a light harvester and the polar heads as CO<sub>2</sub>-capturing sites.

 Received 22nd January 2022  
 Accepted 17th February 2022

DOI: 10.1039/d2ra00453d

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

Carbon dioxide (CO<sub>2</sub>) recycling technologies for the reduction of carbon footprints are crucial because the concentration of CO<sub>2</sub> in the atmosphere has kept increasing from 280 ppm in the preindustrial era to the current level of 410 ppm, driving global warming.<sup>1–6</sup> Technologies to capture, store and convert CO<sub>2</sub> directly from air are thus indispensable for stabilizing or decreasing the concentration of atmospheric CO<sub>2</sub>. Furthermore, it is greatly beneficial when both capture and conversion of CO<sub>2</sub> can be simultaneously carried out in the air. Because the sources of CO<sub>2</sub> emission are widely distributed over the world,

not limited to point sources such as power plants and industrial factories, localized CO<sub>2</sub> capture and storage facilities are not adequate to achieve the goal for the CO<sub>2</sub> reduction. Technologies for direct capture of CO<sub>2</sub> from ambient air and immediate conversion to useful fuels and chemicals such as formaldehyde, methanol and methane should thus be a strong requirement to prevent a drastic increase in CO<sub>2</sub> concentration.

One of the most effective approaches for this goal is to use photocatalysts for both CO<sub>2</sub> capturing and reducing, environmentally friendly harvesting and utilizing solar energy, which has received a lot of attention. Carbon nitride,<sup>7</sup> metal-organic frameworks (MOFs),<sup>8,9</sup> surface-modified metal oxide semiconductor nanocrystals such as TiO<sub>2</sub>,<sup>10,11</sup> nanocomposites of TiO<sub>2</sub> and MOFs,<sup>12</sup> and metal chalcogenides/nitrides<sup>13</sup> have been investigated for CO<sub>2</sub> capture and photocatalytic reduction. Photocatalysis based on conjugated polymers is also a promising candidate for both CO<sub>2</sub> capture and photoconversion reaction. It's because, as proven by polymeric photovoltaic systems, one may take advantages of conjugated polymers' chemical stability<sup>14,15</sup> and outstanding light harvesting properties over a broad range of solar energy from ultraviolet (UV), visible, to near infrared (NIR) light by easily tuning their molecular structure.<sup>16–18</sup> However, CO<sub>2</sub>-fixation has been regarded as the most difficult barrier to overcome in order to improve overall efficiency.<sup>19</sup> Only a few investigations on CO<sub>2</sub> capture and photoreduction based on conjugated polymers have been

<sup>a</sup>Department of Material Science and Engineering, Texas A&M University, College Station, TX 77843, USA

<sup>b</sup>Department of Intelligent Energy and Industry, School of Chemical Engineering and Materials Science, Chung-Ang University, Seoul 06974, Republic of Korea. E-mail: [jjpark@cau.ac.kr](mailto:jjpark@cau.ac.kr)

<sup>c</sup>UNIST Central Research Facilities, Ulsan National Institute of and Technology (UNIST), Ulsan 44919, Republic of Korea. E-mail: [tjshin@unist.ac.kr](mailto:tjshin@unist.ac.kr)

<sup>d</sup>C1 Gas & Carbon Convergent Research Center, Chemical & Process Technology, Korea Research Institute of Chemical Technology, Daejeon 34114, Republic of Korea

<sup>e</sup>Pohang Accelerator Laboratory, Pohang 37673, Republic of Korea

<sup>f</sup>Graduate School of Semiconductor Materials and Devices Engineering, Ulsan National Institute of Science and Technology (UNIST), Ulsan 44919, Republic of Korea

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d2ra00453d



undertaken, including CO<sub>2</sub> adsorption to ionic liquid and subsequent photochemical conversion by conjugated polymers,<sup>20</sup> and conjugated microporous polymers.<sup>21</sup> Thus, a process for effective CO<sub>2</sub> fixation is in great demand for photocatalytic CO<sub>2</sub> conversion based on conjugated polymers.

Numerous investigations on capturing and storing CO<sub>2</sub> have been reported in the field of CO<sub>2</sub> fixation.<sup>22–24</sup> CO<sub>2</sub> gas can be collected in a variety of ways<sup>25</sup> that include physical adsorption without any chemical reactions<sup>22,26</sup> and chemisorption with a chemical reaction such as the production of carbamic acid with an amine<sup>1,27–29</sup> or mineral salts.<sup>2,30</sup> Low interfacial energy, which derives from high polarity, and a large surface area are critical elements for improving capture efficiency in both physisorption and chemisorption.<sup>10,12</sup> As a result, materials having a wide surface area and electrostatic or chemical attraction sites, such as amine compounds,<sup>1,27</sup> inorganic salts, covalent organic frameworks,<sup>22,24,27</sup> and metal–organic frameworks,<sup>5,31</sup> have been proposed for CO<sub>2</sub> fixation.

We expect conjugated polymer nanomaterials assembled with phospholipids to provide both CO<sub>2</sub> collecting sites and photocatalysis *via* conjugated polymers, as well as nano-dimensions for a large surface area. Phospholipids that include phosphocholine (PC) and phosphorus amine<sup>23</sup> are the most abundant lipids, with significant polarity due to phosphorus-based zwitterions in their head groups. These differently charged neighboring groups contain both positive and negative areas in a molecule to maximize polarity and generate dipole polarization to neighbour nonpolar but dipolar molecules,<sup>28</sup> making them a promising candidate for CO<sub>2</sub> capturing sites. Phospholipids, on the other hand, can form a bilayer structure with high polar boundaries and hydrophobic intermediate layer, as seen in cell membranes, by compact packing of polar heads and alkyl tails.<sup>32–36</sup> As we previously demonstrated, conjugated polymers can be integrated into the intermediate layer by alkyl chain association between the polymers' side chains and the phospholipids' tails, resulting in nanoparticles with a hydrophobic polymer core and an outer surface made up of polar lipid heads,<sup>37–39</sup> which can be employed for photocatalysis.<sup>40,41</sup> Such integration of organic and polymeric semiconductors in the intermediate layer of the lipid bilayer and increased charge transfer efficiency<sup>42</sup> were also demonstrated for microbial fuel cells,<sup>43</sup> membrane sensors<sup>44–46</sup> and photocurrent generation systems.<sup>47</sup> Based on these findings, we presume that conjugated polymers in the nanomaterials' core area can efficiently harvest solar energy, and that charges can be carried to the nanomaterials' outer polar surfaces, where CO<sub>2</sub> can be adsorbed.

As a starting point for CO<sub>2</sub> conversion using assemblies of phospholipids and conjugated polymers, we studied the structure variation during polar and nonpolar gas adsorption in a model lipid bilayer film using 1,2-diphytanoyl-*sn*-glycero-3-phosphocholine (D7PC) and a highly crystalline conjugated polymer, poly(3-hexylthiophene) (P3HT), as shown in Fig. 1a. D7PC is a phosphocholine lipid with an alkyl chain length that is similar to that of P3HT, resulting in a densely packed structure with exposed polar head groups that bind polar gas molecules. We confirmed the selective physisorption between

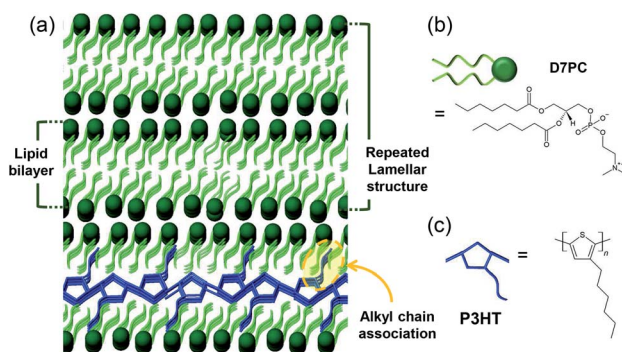


Fig. 1 Schematic image of (a) P3HT-lipid bilayer structure for CO<sub>2</sub> adsorption and conjugate polymer annealing effect and molecular structure of (b) lipid, D7PC and (c) P3HT.

external gases and lipid head groups in the film assembly structure and revealed that the effect of gas adsorption on the assembly structure and optical property of the conjugated polymer in the intermediate layer. By analyzing the structure and intermolecular interaction variation in the assemblies of phospholipids and conjugated polymers, we were able to better understand the role of each section of lipids during gas adsorption and highlight the potential for photocatalytic application.

## 2. Experimental

### 2.1 Materials

Regioregular P3HT was purchased from 1-Material (Quebec, Canada). D7PC in a 25 mg mL<sup>-1</sup> chloroform solution were obtained from Avanti Polar Lipids (Alabama, USA). All chemicals were used without further purification.

### 2.2 Preparation of P3HT–D7PC lipid bilayer film

First, 0.2 mg of P3HT (molecular weight (MW) = 166.28 g mol<sup>-1</sup> on a repeat unit basis, 1.2 μmol) was dissolved in 2 mL of chloroform. Then, 6 μmol of lipid (5 times larger than the molar amount of P3HT) was added to the P3HT chloroform solution (0.116 mL of D7PC solution, 2.89 mg of D7PC (MW = 481.56 g mol<sup>-1</sup>)) and ultrasonicated for 5 min. Uniform films were fabricated by evaporating the solvent in an oil bath at 32 °C while blowing a gentle stream of N<sub>2</sub>. For further drying, the films were stored in vacuum at room temperature overnight. For a control sample, a P3HT film was prepared *via* the same method without the addition of the lipid solution. For measurements of infrared (IR) spectra, surface morphology, and grazing-incidence X-ray diffraction (GIXD), film samples were assembled on silicon substrates or quartz plates and scraped from substrates for gas adsorption examination.

### 2.3 First principle calculation

The selectivity of CO<sub>2</sub> gas absorption behavior was calculated by first-principle calculations based on density functional theory (DFT). The entire calculation has employed B3LYP hybrid functional with a 6-311++G basis set, which is a highly reliable



exchange-correlation functional in terms of precision and calculation resource. All atomic and electronic structures were first optimized at the relaxed states, and the lowest energy structures were obtained for further absorption energy analysis using Gaussian 16 package program.

## 2.4 Characterizations

Gas adsorption isotherms were recorded on an ASAP 2020 volumetric adsorption apparatus (Micromeritics, USA) at a range of absolute pressures from 0 to 870 mmHg for N<sub>2</sub> and CO<sub>2</sub> at 273 K. The samples were degassed in the degas port of the adsorption analyzer at 298 K for 12 h before measurement. Fourier-transform IR (FT-IR) absorption spectra were obtained in reflection mode in the range of 600 to 4000 cm<sup>-1</sup> with a Hyperion 3000 FTIR microscope and a Vertex 80/v FTIR spectrometer equipped at PLS-II 12D IRS beamline of Pohang Accelerator Laboratory in Korea. Phase images of the polymer films were obtained *via* atomic force microscopy (AFM, Nanoscope III, Veeco Instruments, Inc.). Contact-angle images were obtained using a drop-shape analyzer (DSA100S, KRUSS, Germany) *via* the sessile drop method. Synchrotron grazing-incidence X-ray diffraction (GIXD) measurements were conducted at the PLS-II 6D UNIST-PAL beamline. The X-rays emitted from the bending magnet were monochromated at 11.6 keV (wavelength: 1.0688 Å) using Si(111) double crystals and were focused on the detector by using a combination of a sagittal-type monochromator crystal and a toroidal mirror system. The incident angle of the X-ray beams was set at 0.13°, and the sample-to-detector distance was approximately 246 mm. The diffraction patterns were recorded with a two-dimensional (2D) charge-coupled device detector (MX225-HS, Rayonix LLC, USA) and the diffraction angles were calibrated using a lanthanum hexaboride (LaB<sub>6</sub>) standard material (NIST SRM 660c). Ultraviolet-visible (UV-vis) absorption spectra were obtained using a UV-vis spectrometer (V-670, JASCO, Japan).

## 3. Results and discussions

### 3.1 Selective gas adsorption

The polar head group in D7PC, highly polarized phosphate choline, has been shown by DFT calculations to have the ability to attract polar gas molecules. Charge distributions of lipids based on DFT calculations (Fig. 2a and b) demonstrate that the phosphocholine group strongly polarizes with electron-deficient choline group (blue) and electron-rich phosphor group (red), resulting in partial polarization of the gas molecules.<sup>48</sup> The partially negative oxygen atom in CO<sub>2</sub> interacts with the choline group and the partially positive carbon in CO<sub>2</sub> interacts with the phosphor group due to electrostatic attraction.<sup>49,50</sup> In comparison to N<sub>2</sub> molecules, the CO<sub>2</sub> molecule is more likely to be stabilized closer to the lipid head group. The distance between the choline group and the gas molecules was calculated to be 3.421 Å in CO<sub>2</sub> adsorption and 3.710 Å in N<sub>2</sub>, whereas the distance between the phosphor group and the gas was 2.472 Å in CO<sub>2</sub> and 2.990 Å in N<sub>2</sub>. CO<sub>2</sub> adsorption energies eventually reached  $-1.49 \text{ kJ mol}^{-1}$ , about three times higher

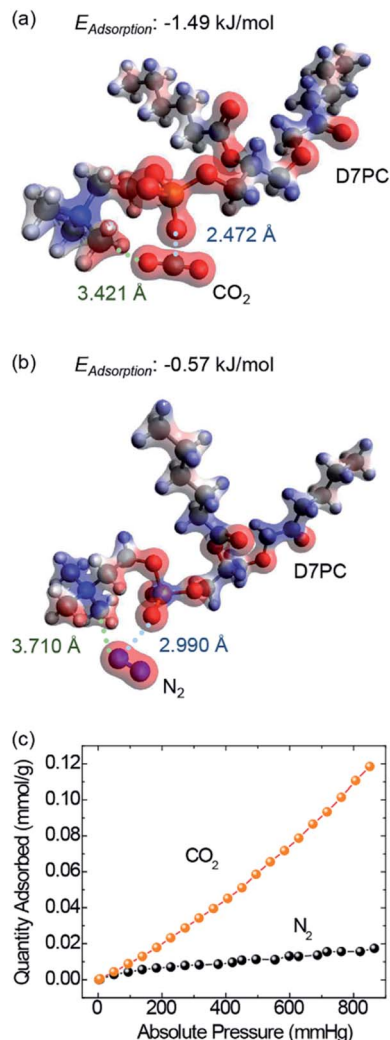


Fig. 2 DFT model for calculating the interaction between lipid (D7PC) and (a) CO<sub>2</sub> and (b) N<sub>2</sub> gas molecules. (c) Adsorption of N<sub>2</sub> (black dots) and CO<sub>2</sub> (orange dots) based on a BET analysis at 273 K for the P3HT-D7PC film.

than N<sub>2</sub> adsorption energies of  $-0.57 \text{ kJ mol}^{-1}$ . The DFT calculations demonstrate that D7PC may preferentially adsorb gas molecules and that it is primarily made up of phosphocholine groups, which are polar head groups that cause dipole interaction. The selective adsorption of N<sub>2</sub> and CO<sub>2</sub> was evaluated using a Brunauer-Emmett-Teller (BET) analysis (Fig. 2c) in agreement with the DFT calculations. The amount of CO<sub>2</sub> gas adsorbed into 1 g of the P3HT-D7PC lipid bilayer film at 760 mmHg was 0.102 mmol, over six times higher than that of N<sub>2</sub> (0.016 mmol). This indicates that CO<sub>2</sub> was attracted to the polar head group by electrostatic interaction with induced polarization.

FT-IR spectroscopy was used to analyze the intermolecular interaction between D7PC and CO<sub>2</sub> molecules as experimental evidence for DFT computations (Fig. 3 and S1†). D7PC and D7PC-P3HT films were assembled on Si wafers and used for reflected mode measurements. The D7PC and D7PC-P3HT films' FT-IR spectra were collected sequentially in three

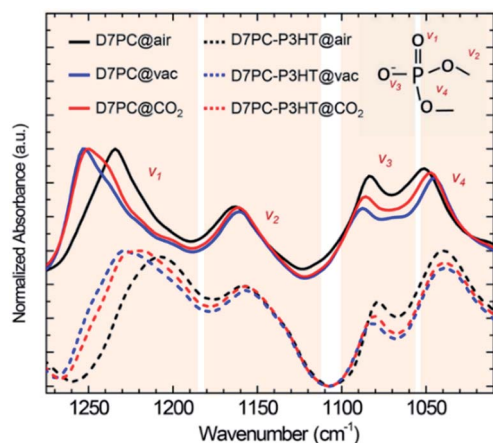


Fig. 3 Normalized FT-IR absorbance spectra in 1300 to 1000  $\text{cm}^{-1}$  range of D7PC (solid line) and D7PC/P3HT film (dashed line) in air (black), vacuum (blue) and  $\text{CO}_2$  (red) condition.

different environments: air (@air), vacuum for 15 minutes of degassing (@vac), and finally 30 minutes of  $\text{CO}_2$  purging (@ $\text{CO}_2$ ). Fig. 3 shows normalized absorbance spectra in the range of 1300–1000  $\text{cm}^{-1}$  for assessing any variations in phosphate bonds. The phosphate group's four IR bands were allocated to terminated bonds (1250–1220  $\text{cm}^{-1}$ ,  $\nu_1(\text{P}=\text{O})$ ) and 1190–1070  $\text{cm}^{-1}$ ,  $\nu_3(\text{P}-\text{O}^-)$ , and bonds connected to choline (1170–1055  $\text{cm}^{-1}$ ,  $\nu_2$ ) and alkyl tails (1140–1000  $\text{cm}^{-1}$ ,  $\nu_4$ ).<sup>51,52</sup> Variations in the environment had a significant impact on the terminated bands that were exposed to the media. When ambient air was removed, the peak attributed to  $\nu_1$  in the spectrum for D7PC–P3HT film (dashed lines in Fig. 3) was displaced from 1234 to 1253  $\text{cm}^{-1}$ , then restored to 1240  $\text{cm}^{-1}$  following  $\text{CO}_2$  purging. This finding indicates that  $\text{CO}_2$  might be put near the terminal bonds and pull electrons from the electron-rich oxygen molecule, resulting in a lower force constant and the shorter interatomic distance between carbon in  $\text{CO}_2$  and oxygen in the  $\text{P}=\text{O}$  bond as calculated by DFT. The wavenumber of the peak assigned to  $\nu_3(\text{P}-\text{O}^-)$  followed the same pattern, varying from 1078, 1082, and 1080  $\text{cm}^{-1}$  in air, vacuum, and  $\text{CO}_2$ , respectively, but the change was not as pronounced as it was in  $\nu_1$ .

Meanwhile, even after  $\text{CO}_2$  purging, the peaks assigned to  $\nu_2$  and  $\nu_4$  remained unchanged at 1159 and 1039  $\text{cm}^{-1}$ . Because of their relationship to heavy alkoxy groups, these two bonds were situated opposite the bonds exposed to the environment, correcting electron distribution, and their bond strengths were unaffected by the environment. All of these findings point to  $\text{P}=\text{O}$  and  $\text{CO}_2$  as the primary intermolecular interaction between D7PC and  $\text{CO}_2$  molecules. It's worth noting that the IR spectra of D7PC reveal a somewhat different pattern for  $\nu_4$ , despite the fact that the patterns for  $\nu_1$ ,  $\nu_2$ , and  $\nu_3$  are similar to those of D7PC–P3HT. For measurements in air, vacuum, and  $\text{CO}_2$ , the peak of  $\nu_4$  varies from 1051, 1045, and 1047  $\text{cm}^{-1}$ , respectively (solid lines in Fig. 3). These findings suggest that when alkyl tails are coupled with alkyl side chains of P3HT *via*

hydrophobic interactions, the P–O bond connected to lipid tails is less influenced by environmental change.

### 3.2 Structural and optical characteristics

Surface morphologies and any structural features of films were investigated by utilizing AFM. Fig. 4a and b show a P3HT film generated by  $\text{N}_2$  blowing with an uneven surface morphology and a roughness of 1.23 nm. The D7PC–P3HT film, on the other hand, produced a remarkably homogenous, smooth surface with a roughness of 0.194 nm. P3HT and D7PC–P3HT films have contact angles of  $90^\circ \pm 1^\circ$  and  $9^\circ \pm 1^\circ$ , respectively. These findings show that P3HT chains are embedded in the D7PC bilayer's alkyl intermediate region, and that the D7PC–P3HT film's outermost surface is made up of D7PC polar heads, which

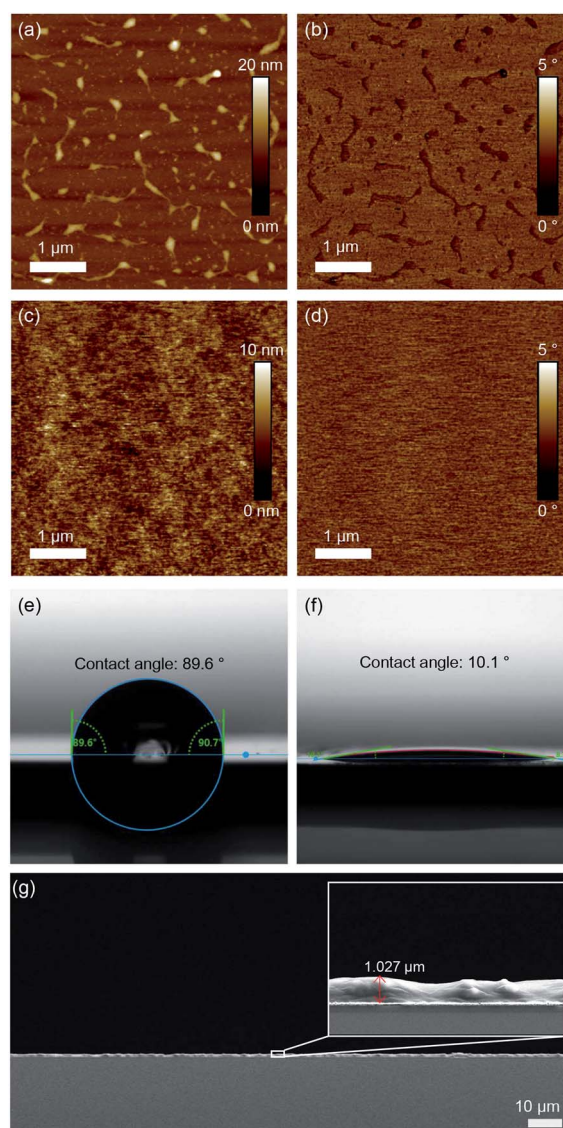


Fig. 4 AFM height and phase images of the (a and b) P3HT film and (c and d) P3HT–D7PC film. Contact-angle images of the (e) P3HT film and (f) P3HT–D7PC film. (g) A cross-sectional SEM image of P3HT–D7PC film.



are hydrophilic.<sup>53,54</sup> The thickness of assembled films was in a range from 200 nm to a few micrometer, which was irregular due to our film preparation process by nitrogen blowing. In a uniformly coated region on the silicon substrate, it was about 1  $\mu\text{m}$  as shown in Fig. 4g.

We investigated *in situ* GIXD patterns in vacuum and during  $\text{CO}_2$  adsorption to observe if there was any structural alteration due to gas adsorption on the D7PC–P3HT film. Fig. 5a, b, and c show 2D GIXD patterns of P3HT, D7PC, and D7PC–P3HT films recorded in vacuum on silicon wafers, with their line cuts along in-plane (Fig. 5d) and out-of-plane (Fig. 5e) directions, respectively. The pristine P3HT film has a highly ordered edge-on structure, vertically aligned with the  $z$ -axis, as shown in the 2D GIXD image in Fig. 5a. The (100) lamellar stacking peak of P3HT chains, which is strongest in the  $z$ -direction, is ascribed to the most conspicuous peak that appears as a ring pattern at  $q = 0.364 \text{ \AA}^{-1}$  ( $d$ -spacing = 17.262  $\text{\AA}$ ). As illustrated by the red-colored line in Fig. 5e, more repeating lamella peaks arise at  $q_{rz} = 0.744 \text{ \AA}^{-1}$  and  $1.130 \text{ \AA}^{-1}$  for the (200) and (300) planes, respectively, which are similar to a scattering pattern of a P3HT film in literature.<sup>55</sup> Additionally, the clear peak of (010) plane characteristic for  $\pi$ - $\pi$  stacking ( $q_{xy} = 1.622 \text{ \AA}^{-1}$ ,  $d$ -spacing = 3.874  $\text{\AA}$ ) and a weak but distinguishable peak of alkyl chain association ( $q_{xy} = 1.4 \text{ \AA}^{-1}$ ,  $d$ -spacing = 4.5  $\text{\AA}$ ) were observed, supporting the edge-on structure of the pristine P3HT film, as indicated by the red line in Fig. 5d (the 1D line cut of the P3HT film scattering pattern along in-plane direction).<sup>55</sup> The (100) peak, on the other hand, also emerges in the  $q_{xy}$  1D plot, showing that the P3HT was substantially crystallized but that some of the crystal domain was scattered randomly.

The D7PC film, on the other hand, shows a densely packed lamellar structure with recurrent peaks in the  $z$ -direction at  $q_{rz}$

= 0.204, 0.398, 0.816, 1.025, 1.232, and  $1.439 \text{ \AA}^{-1}$  for (100), (200), (400), (500), (600), and (700), which are similar to literature.<sup>56</sup> The calculated lipid bilayer thickness of 30.80  $\text{\AA}$  is similar to that of D7PC's liquid crystalline phase (L phase, 30.14  $\text{\AA}$ ).<sup>57</sup> Because of the packing of lipid molecules, the bilayer structure is also packed in a plane orientation. Three distinct peaks can be seen in Fig. 5b and d:  $q_{xy} = 1.314 \text{ \AA}^{-1}$  ( $d$ -spacing = 4.782  $\text{\AA}$ ),  $q_{xy} = 1.500 \text{ \AA}^{-1}$  ( $d$ -spacing = 4.109  $\text{\AA}$ ), and  $q_{xy} = 1.624 \text{ \AA}^{-1}$  ( $d$ -spacing = 3.869  $\text{\AA}$ ). The peak at  $q_{xy} = 1.314 \text{ \AA}^{-1}$  is due to packing of liquid alkyl chains in a lamellar structure, while the other two peaks are due to alkyl chain packing in an orthorhombic crystalline structure. These findings suggest that D7PC film's liquid crystalline structure is a mix of liquid lamellar and orthorhombic crystalline structures, comparable to the lipid assembly structure in the stratum corneum.<sup>58</sup>

The GIXD pattern of the D7PC–P3HT assembly is similar to that of the D7PC assembly. It has a lipid bilayer thickness of 29.778  $\text{\AA}$  ( $q = 0.211 \text{ \AA}^{-1}$ ), which is somewhat less than the bilayer thickness of D7PC alone (30.8  $\text{\AA}$ ). It's also worth noting that the peak at  $q_{xy} = 1.3 \text{ \AA}^{-1}$  persists, whereas the peaks at  $q_{xy} = 1.5$  and  $1.6 \text{ \AA}^{-1}$  vanish. These results indicate that the alkyl chain packing with the orthorhombic crystalline structure is disrupted when P3HT chains are assembled with D7PC molecules, with only an interchain spacing between alkyl chains in the liquid lamellar structure. The D7PC–P3HT, on the other hand, does not have lamellar peaks in the (200) and (300) planes for the crystalline P3HT assembly. At  $q = 0.364 \text{ \AA}^{-1}$ , only the peak of the (100) plane of the P3HT assembly is visible, which is overlapped with the peak of the (200) plane for D7PC. These findings strongly suggest that P3HT chains do not form a self-domain in its crystalline structure and are bound to D7PC *via* alkyl chain association, with D7PC's lamellar structure

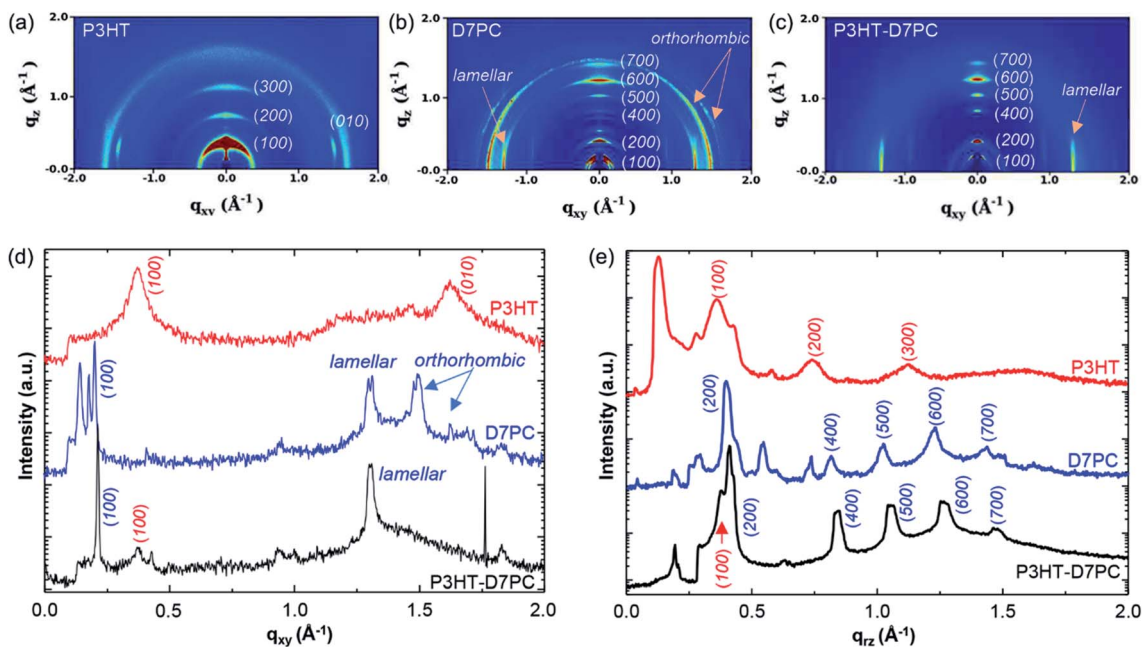


Fig. 5 GIXD 2D images of (a) P3HT film, (b) D7PC film, and (c) D7PC–P3HT film in a vacuum condition. (d) 1-D  $q_{xy}$  plots and (e)  $q_{rz}$  plots of P3HT (red), D7PC (blue) and P3HT–D7PC composite (black).



dominating D7PC–P3HT assembly. These results also indicate that the D7PC–P3HT assembly exhibits a slightly reduced bilayer thickness because the D7PC bilayer structure is constricted by the presence of P3HT *via* alkyl chain association outside of the D7PC domain.

The structural change of the D7PC-only and D7PC–P3HT assemblies with gas absorption was studied using *in situ* GIXD measurements with purging N<sub>2</sub> and CO<sub>2</sub> gases. 2D GIXD patterns of the assemblies were recorded every 10 seconds to examine the gas environment conditions. Both assemblies in vacuum ( $\sim 5 \times 10^{-2}$  Torr) revealed a lamellar structure with distinct alkyl chain packing peaks (red arrows) in the in-plane direction and layering peaks in the out-of-plane direction, as shown in Fig. 6a and b. However, depending on the types of gases, they displayed distinct structural variations upon gas adsorption after purging them. With N<sub>2</sub> purging (540 Torr), the strong diffraction peaks of the lamellar and alkyl chain packing were sustained for up to 15 minutes (Fig. 6a at an intensity maximum of 500 and Fig. S2† at that of 380). On the other hand, the strength of the lamellar and alkyl chain packing peaks is considerably reduced within 1 min after CO<sub>2</sub> purging (540 Torr) as shown in Fig. 6b at an intensity maximum of 500 and Fig. S3†

at that of 380. These findings indicate that CO<sub>2</sub> molecules are quickly adsorbed onto the D7PC–P3HT assembly and pierced into the lipid bilayer, disrupting the assembly's ordered structure, whereas N<sub>2</sub> gas molecules are difficult to adsorb and penetrate into the assembly.

The ordered assembly structure is recovered to its original structure when the sample was purged with N<sub>2</sub> for 40 min and then vacuumed for 20 min (Fig. S2†), but not fully recovered when the sample was purged with CO<sub>2</sub> (Fig. S3†). These results suggest that structural changes generated by N<sub>2</sub> purging and vacuuming are reversible, whereas those caused by CO<sub>2</sub> gas molecules adsorption and penetration are not. Furthermore, as shown in Fig. 6c and d, repeated vacuuming for 20 min and CO<sub>2</sub> purging for 40 min rearranged alkyl chains into an orderly structure. With repeated vacuuming and CO<sub>2</sub> purging, the diffraction peaks of P3HT's (100) plane at  $q \sim 0.38 \text{ \AA}^{-1}$  and D7PC's alkyl chain packing peak at  $q \sim 1.3 \text{ \AA}^{-1}$  become clearer, as demonstrated in the 1D line cut along the in-plane direction measured in vacuum (Fig. 6c) (note: the samples used in Fig. 6c and d are thinner than the samples used in Fig. 6b, resulting in less sharp diffraction patterns in vacuum). Azimuthal cut profiles for the diffraction peak of alkyl chain packing at  $q \sim 1.3$

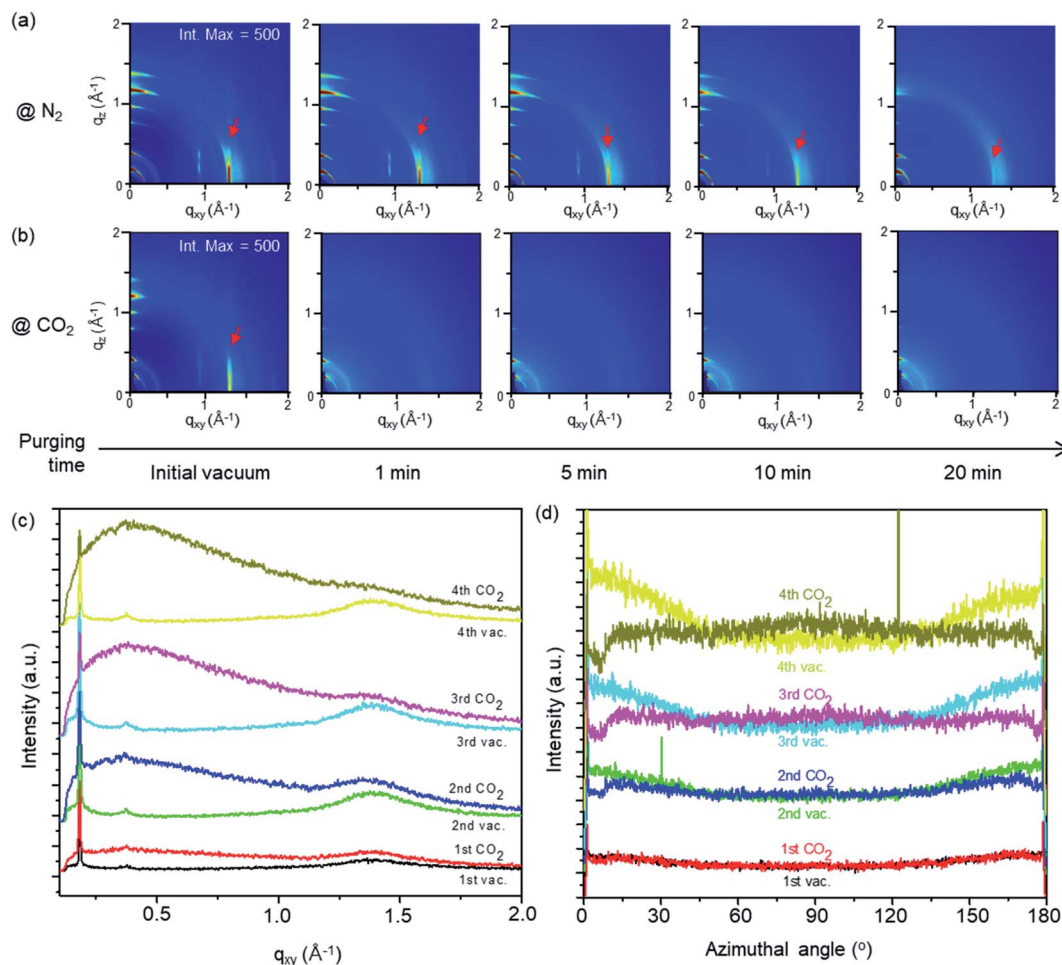


Fig. 6 2D GIXD images of D7PC–P3HT assembly in (a) N<sub>2</sub> and (b) CO<sub>2</sub> purging condition and (c)  $q_{xy}$  plots in a repeated vacuuming and CO<sub>2</sub> purging. (d) Azimuthal cut profiles of alkyl chain diffraction at  $q \sim 1.3 \text{ \AA}^{-1}$ .



$\text{\AA}^{-1}$  (Fig. 6d) show increased intensity at around 0 and  $180^\circ$ , suggesting that alkyl chains are vertically organized on the substrate surface after repeated vacuuming and  $\text{CO}_2$  purging. Our findings present that  $\text{CO}_2$  can be easily absorbed and penetrated into a lipid bilayer assembly, allowing lipid molecules to reorganize themselves into an ordered structure. Furthermore, with repeated vacuuming and purging processes, increased gas scattering intensity, seen as an amorphous hollow below  $q$   $1.0 \text{\AA}^{-1}$  in Fig. 6c, suggests that some  $\text{CO}_2$  is trapped in the assembly even after the vacuuming process.

We examined the effect of  $\text{CO}_2$  treatment on the optical properties of P3HT assembled with the D7PC. The optical absorbance measured with samples assembled on a transparent slide indicated that the aligned alkyl chains in the D7PC–P3HT assembly improved the absorption property of P3HT, as shown in Fig. 7. The absorbance of the D7PC–P3HT assembly was red-shifted to 564 nm (red dotted line in Fig. 7) in vacuum, compared to 520 nm for the pure P3HT film (black dotted line), which is assigned to  $S_1$  band transition.<sup>59</sup> There was also a second absorption band at 606 nm, which is assigned to a (0–0) transition of  $S_0$  band in aggregates of P3HT in literature, indicating a bathochromic shift due to improved intra- or intermolecular electron delocalization.<sup>60,61</sup> The maximum intensity ratio of  $S_0/S_1$ , is 0.951, which is unusually high for P3HT based thin films.<sup>52</sup> Then, the two films were placed in a small chamber charged with  $\text{CO}_2$  for 1 hour to confirm the  $\text{CO}_2$  purging action and utilized to measure absorption spectra in ambient atmosphere within 5 min after they were removed from the chamber. Fig. 7 indicates that following  $\text{CO}_2$  charge, the absorption spectrum of the P3HT film (orange solid line) didn't change, whereas the D7PC–P3HT film (blue solid line) showed an even further bathochromic shift of the  $S_0$  band to 611 nm and a higher  $S_0/S_1$  ratio of 0.982. Because we couldn't discover distinct diffraction peaks of the (200) and (300) planes

and  $\pi$ – $\pi$  stacking of P3HT in the assembly with an excess of D7PC used in our investigation, it's unlikely that P3HT forms crystalline aggregates as reported in thin films. Thus, the bathochromic shift of P3HT assembled with D7PC is most likely caused by intramolecular electron delocalization. As predicted by theoretical calculations,<sup>62</sup> such intramolecular electron delocalization is possible by reduced torsional angle and prolonged  $\pi$  conjugation along P3HT backbone. Our analysis shows that  $\text{CO}_2$  adsorption and penetration into the D7PC–P3HT assembly causes compressive strain, and rearrangement of conjugated backbones and alkyl chains for the intramolecular electron delocalization when  $\text{CO}_2$  molecules are muscling with polar heads and alkyl chains.

It is noteworthy that the  $\text{CO}_2$  annealing under supercritical circumstances of  $P = 8\text{--}15 \text{ MPa}$  and  $T = 35\text{--}36^\circ \text{C}$  could plasticize P3HT films and accelerate their crystallization for enhanced charge carrier mobility.<sup>63,64</sup> In our investigation, a similar  $\text{CO}_2$  annealing effect was obtained for the P3HT assembled with D7PC at a lower pressure of 0.072 MPa and room temperature than the critical pressure and temperature of  $\text{CO}_2$ , which is remarkable. We believe that high  $\text{CO}_2$  gas adsorption on D7PC's polar heads and trapping in the assembly plays a key role in the molecular rearrangement.

## 4. Conclusions

As a model system for photochemical reactions of gas molecules based on conjugated polymers, we investigated the gas adsorption property on the assembly films of a phospholipid, D7PC, and a crystalline conjugated polymer, regioregular P3HT. Because the polar heads of D7PC are arrayed on the outermost surface of the films and  $\text{CO}_2$  has a stronger electrostatic attraction to the polar heads than  $\text{N}_2$  gas molecules, a higher amount of  $\text{CO}_2$  than  $\text{N}_2$  gas molecules could be adsorbed onto the assembly films, as confirmed by DFT calculations and experimental results. *In situ* GIXD measurements revealed structural changes based on gas adsorption and penetration into the D7PC–P3HT films.  $\text{CO}_2$  gas molecules are immediately adsorbed on polar heads, disrupting the layering of lipids and alkyl chain packing, and allowing for orderly rearranging of lipid and polymer molecules. The increased intensity of the  $S_0$  band in the absorption spectra of the D7PC–P3HT assembly films was due to enhanced electron delocalization along the conjugated backbones that are embedded in the lipid bilayer *via* alkyl chain association between lipid heptyl tails and ethylhexyl side chains. Our findings suggest that a phospholipid-conjugated polymer assembly could be a promising  $\text{CO}_2$  fixation and photochemical conversion candidate. The well-blended lipid-conjugated polymer films with strong and closer packing between the lipid and conjugated polymer films have the potential to improve  $\text{CO}_2$  accessibility to the photochemical reaction site, resulting in increased conversion efficiency. Furthermore, the aligned conjugated films enable for the development of specialized photochemical processes by enlarging the light absorption range to acceptable energy levels *via* repeated adsorption/desorption. This research presents a lipid-conjugated polymer composite model that has the

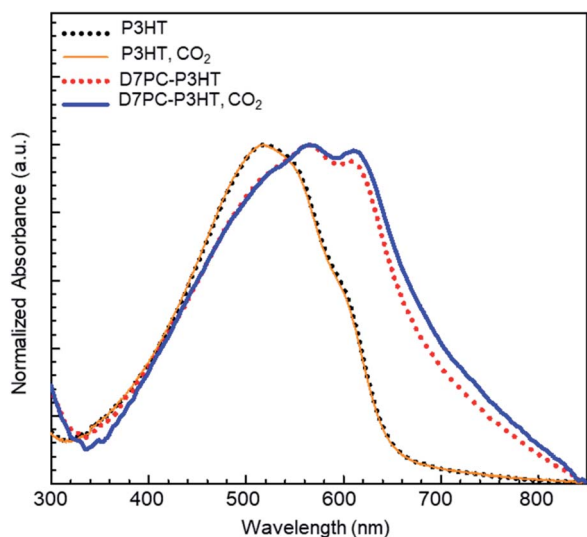


Fig. 7 UV-vis absorbance spectra of pristine P3HT (black dotted line), the P3HT–D7PC composite film (red dotted line),  $\text{CO}_2$ -treated P3HT (orange solid line), and the  $\text{CO}_2$ -treated P3HT–D7PC composite film (blue solid line).



potential to produce a dual fixing and CO<sub>2</sub> conversion system. It should be further emphasized that a new technique should be created to enhance surface area of this system, for example, by manufacturing nanomaterials or porous structures based on this kind of system. In addition, for practical applications, novel amphiphilic materials that feature CO<sub>2</sub> collecting sites and can be combined with conjugated polymers should be manufactured in a cost-effective process to replace expensive phospholipids.

## Author contributions

Juran Noh: formal analysis, investigation, data curation, writing – original draft. Dong Geon Koo: formal analysis, investigation. Chohee Hyun, formal analysis, investigation, resources. Dabin Lee: formal analysis, investigation. Seohyeon Jang: formal analysis, investigation. Jiho Kim: formal analysis, investigation. Yejee Jeon: formal analysis, investigation. Su-Young Moon: formal analysis, investigation, data curation, validation. Boknam Chae: formal analysis, investigation, validation. Inho Nam: formal analysis, investigation, data curation, validation. Juhyun Park: methodology, conceptualization, writing – review & editing, supervision. Tae Joo Shin: methodology, conceptualization, funding acquisition, writing – review & editing, supervision.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was supported by the Chung-Ang University Graduate Scholarship in 2020, and the National Research Foundation of Korea (Grant No. NRF-2018R1A5A1025224). The authors thank Seong-hun Lee and Juhyun Yang, who helped with the GIXD experiments. Synchrotron X-ray Experiments at PLS-II 6D and 12D beamlines were supported in part by UCRF, MSIP, and POSTECH.

## References

- 1 F. Inagaki, C. Matsumoto, T. Iwata and C. Mukai, *J. Am. Chem. Soc.*, 2017, **139**, 4639–4642.
- 2 H.-J. Ho, A. Iizuka and E. Shibata, *Ind. Eng. Chem. Res.*, 2019, **58**, 8941–8954.
- 3 N. Kittner, F. Lill and D. M. Kammen, *Nat. Energy*, 2017, **2**, 17125.
- 4 V. Scott, R. S. Haszeldine, S. F. B. Tett and A. Oschlies, *Nat. Clim. Change*, 2015, **5**, 419–423.
- 5 J. Liang, Y.-B. Huang and R. Cao, *Coord. Chem. Rev.*, 2019, **378**, 32–65.
- 6 X. Shi, H. Xiao, H. Azarabadi, J. Song, X. Wu, X. Chen and K. S. Lackner, *Angew. Chem., Int. Ed.*, 2020, **59**, 6984–7006.
- 7 S. N. Talapaneni, G. Singh, I. Y. Kim, K. AlBahily, A. H. Al-Muhtaseb, A. S. Karakoti, E. Tavakkoli and A. Vinu, *Adv. Mater.*, 2020, **32**, e1904635.
- 8 S. Wang and X. Wang, *Angew. Chem., Int. Ed.*, 2016, **55**, 2308–2320.
- 9 I. I. Alkhatib, C. Garlisi, M. Pagliaro, K. Al-Ali and G. Palmisano, *Catal. Today*, 2020, **340**, 209–224.
- 10 J. Low, B. Cheng and J. Yu, *Appl. Surf. Sci.*, 2017, **392**, 658–686.
- 11 Y. Liao, S. W. Cao, Y. Yuan, Q. Gu, Z. Zhang and C. Xue, *Chem.–Eur. J.*, 2014, **20**, 10220–10222.
- 12 A. Crake, K. C. Christoforidis, A. Kafizas, S. Zafeiratos and C. Petit, *Appl. Catal., B*, 2017, **210**, 131–140.
- 13 D. Adekoya, M. Tahir and N. A. S. Amin, *Renewable Sustainable Energy Rev.*, 2019, **116**, 1093898.
- 14 R. Prabhu, B. Roopashree, T. Jeevananda, S. Rao, K. Raghava Reddy and A. V. Raghu, *Mater. Sci. Energy Technol.*, 2021, **4**, 92–99.
- 15 R. Prabhu, T. Jeevananda, K. R. Reddy and A. V. Raghu, *Mater. Sci. Energy Technol.*, 2021, **4**, 107–112.
- 16 J. Park, *J. Ind. Eng. Chem.*, 2017, **51**, 27–43.
- 17 M. Liras, M. Barawi and V. A. de la Pena O'Shea, *Chem. Soc. Rev.*, 2019, **48**, 5454–5487.
- 18 C. Dai and B. Liu, *Energy Environ. Sci.*, 2020, **13**, 24–52.
- 19 S. Dang, H. Yang, P. Gao, H. Wang, X. Li, W. Wei and Y. Sun, *Catal. Today*, 2019, **330**, 61–75.
- 20 Y. Chen, G. Ji, S. Guo, B. Yu, Y. Zhao, Y. Wu, H. Zhang, Z. Liu, B. Han and Z. Liu, *Green Chem.*, 2017, **19**, 5777–5781.
- 21 H.-P. Liang, A. Acharjya, D. A. Anito, S. Vogl, T.-X. Wang, A. Thomas and B.-H. Han, *ACS Catal.*, 2019, **9**, 3959–3968.
- 22 X. Zhu, C. Tian, G. M. Veith, C. W. Abney, J. Dehaut and S. Dai, *J. Am. Chem. Soc.*, 2016, **138**, 11497–11500.
- 23 Y. Chen, H. Sun, R. Yang, T. Wang, C. Pei, Z. Xiang, Z. Zhu, W. Liang, A. Li and W. Deng, *J. Mater. Chem. A*, 2015, **3**, 87–91.
- 24 K. Wang, H. Huang, D. Liu, C. Wang, J. Li and C. Zhong, *Environ. Sci. Technol.*, 2016, **50**, 4869–4876.
- 25 Z. H. Ban, L. K. Keong and A. Mohd Shariff, *Adv. Mater. Res.*, 2014, **917**, 134–143.
- 26 X. Sun, D. Li, W. Gao and H. Yin, *Nanotechnology*, 2021, **32**, 065601.
- 27 H. J. Kwon, C. Lee, J.-W. Kook, J. H. Kim, K. Hwang and J.-Y. Lee, *Macromol. Res.*, 2021, **28**, 1289–1296.
- 28 H. Coskun, A. Aljabour, P. De Luna, D. Farka, T. Greunz, D. Stifter, M. Kus, X. Zheng, M. Liu, A. W. Hassel, W. Schöfberger, E. H. Sargent, N. S. Sariciftci and P. Stadler, *Sci. Adv.*, 2017, e1700686.
- 29 F. Li, S. Zeng, Y. Bai, H. Dong, H. Wang, X. Ji and X. Zhang, *Energy Fuels*, 2020, **34**, 8526–8533.
- 30 B. Yang, L. Wang, Z. Hua and L. Guo, *Ind. Eng. Chem. Res.*, 2019, **58**, 9838–9843.
- 31 Y. Yu, Q.-G. Yin, L.-J. Ye and H. Yu, *Macromol. Res.*, 2021, **29**, 605–612.
- 32 Y. Zhang, X. Wang, S. Ma, K. Jiang and X. Han, *RSC Adv.*, 2016, **6**, 11325–11328.
- 33 L. Bechtella, C. Kirschbaum, M. Cosset, G. Clodic, L. Matheron, G. Bolbach, S. Sagan, A. Warrant and E. Sachon, *Anal. Chem.*, 2019, **91**, 9102–9110.
- 34 P. O. Saboe, E. Conte, S. Chan, H. Feroz, B. Ferlez, M. Farell, M. F. Poyton, I. T. Sines, H. Yan, G. C. Bazan, J. Golbeck and M. Kumar, *J. Mater. Chem. A*, 2016, **4**, 15457–15463.



- 35 F. Ito, Y. Nishiyama, S. Duan and H. Yamada, *Macromol. Res.*, 2019, **28**, 365–372.
- 36 I. O. L. Bacellar, M. C. Oliveira, L. S. Dantas, E. B. Costa, H. C. Junqueira, W. K. Martins, A. M. Durantini, G. Cosa, P. Di Mascio, M. Wainwright, R. Miotto, R. M. Cordeiro, S. Miyamoto and M. S. Baptista, *J. Am. Chem. Soc.*, 2018, **140**, 9606–9615.
- 37 J. Yoon, J. Kwag, T. J. Shin, J. Park, Y. M. Lee, Y. Lee, J. Park, J. Heo, C. Joo, T. J. Park, P. J. Yoo, S. Kim and J. Park, *Adv. Mater.*, 2014, **26**, 4559–4564.
- 38 Y. K. Choi, D. Lee, S. Y. Lee, T. J. Shin, J. Park and D. J. Ahn, *Macromolecules*, 2017, **50**, 6935–6944.
- 39 T.-T. D. Pham, Y. H. Seo, D. Lee, J. Noh, J. Chae, E. Kang, J. Park, T. J. Shin, S. Kim and J. Park, *Polymer*, 2019, **161**, 205–213.
- 40 J. Che, N. Bae, J. Noh, T. Kim, P. J. Yoo, T. J. Shin and J. Park, *Macromol. Res.*, 2019, **27**, 427–434.
- 41 V. Javanbakht and M. Mohammadian, *J. Mol. Struct.*, 2021, **1239**, 130496.
- 42 K. R. Reddy, H. M. Jeong, Y. Lee and A. V. Raghu, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 1477–1484.
- 43 J. P. L. E. Garner, S. M. Dyar, A. Chworos, J. J. Sumner and G. C. Bazan, *J. Am. Chem. Soc.*, 2010, **132**, 10042–10052.
- 44 N. Sakai and S. Matile, *J. Am. Chem. Soc.*, 2018, **140**, 11438–11443.
- 45 T. Nishimura, F. Tamura, S. Kobayashi, Y. Tanimoto, F. Hayashi, Y. Sudo, Y. Iwasaki and K. Morigaki, *Langmuir*, 2017, **33**, 5752–5759.
- 46 B. S. Dakshayini, K. R. Reddy, A. Mishra, N. P. Shetti, S. J. Malode, S. Basu, S. Naveen and A. V. Raghu, *Microchem. J.*, 2019, **147**, 7–24.
- 47 Y. Lee, I. Yang, J. E. Lee, S. Hwang, J. W. Lee, S.-S. Um, T. L. Nguyen, P. J. Yoo, H. Y. Woo, J. Park and S. K. Kim, *J. Phys. Chem. C*, 2013, **117**, 3298–3307.
- 48 R. Raveesha, A. M. Anusuya, A. V. Raghu, K. Yogesh Kumar, M. G. Dileep Kumar, S. B. Benaka Prasad and M. K. Prashanth, *Comput. Toxicol.*, 2022, **21**, 100202.
- 49 B. Pramodh, P. Naresh, S. Naveen, N. K. Lokanath, S. Ganguly, J. Panda, S. Murugesan, A. V. Raghu and I. Warad, *Chem. Data Collect.*, 2021, **31**, 100587.
- 50 S. B. Benaka Prasad, S. Naveen, C. S. Ananda Kumar, N. K. Lokanath, A. V. Raghu, I. Daraghme, K. R. Reddy and I. Warad, *J. Mol. Struct.*, 2018, **1167**, 215–226.
- 51 J. Coates, *Encycl. Anal. Chem.*, 2006, pp. 1–23.
- 52 L. De Marco, M. Thamer, M. Reppert and A. Tokmakoff, *J. Chem. Phys.*, 2014, **141**, 034502.
- 53 D. P. Suhas, T. M. Aminabhavi and A. V. Raghu, *Appl. Clay Sci.*, 2014, **101**, 419–429.
- 54 D. P. Suhas, T. M. Aminabhavi and A. V. Raghu, *Polym. Eng. Sci.*, 2014, **54**, 1774–1782.
- 55 M. Brinkmann, *J. Polym. Sci., Part B: Polym. Phys.*, 2011, **49**, 1218–1233.
- 56 J. Noh, S. Jung, G. Kim, D. G. Koo, K. S. Choi, T. J. Shin, C. Yang and J. Park, *J. Mol. Liq.*, 2019, **288**, 111046.
- 57 D. March, *Handbook of Lipid Bilayers*, CRC Press, 2nd edn, 2013, p. 385.
- 58 W. Stephane Faraci and C. T. Walsh, *Biochemistry*, 1988, **27**, 3267–3276.
- 59 J. Müllerrová, M. Kaiser, V. Nádaždy, P. Šiffalovič and E. Majková, *Sol. Energy*, 2016, **134**, 294.
- 60 F. C. Spano and C. Silva, *Annu. Rev. Phys. Chem.*, 2014, **65**, 477.
- 61 P. J. Brown, D. S. Thomas, A. Köhler, J. S. Wilson, J.-S. Kim, C. M. Ramsdale, H. Sirringhaus and R. H. Friend, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2003, **67**, 064203.
- 62 M. Böckmann, T. Schemme, D. H. de Jong, C. Denz, A. Heuer and N. L. Doltsinis, *Phys. Chem. Chem. Phys.*, 2015, **17**, 28616.
- 63 B. X. Dong, J. A. Amonoo, G. E. Purdum, Y. L. Loo and P. F. Green, *ACS Appl. Mater. Interfaces*, 2016, **8**, 31144–31153.
- 64 N. Jiang, L. Sendogdular, M. Sen, M. K. Endoh, T. Koga, M. Fukuto, B. Akgun, S. K. Satija and C. Y. Nam, *Langmuir*, 2016, **32**, 10851–10860.

