


Cite this: *RSC Adv.*, 2022, 12, 27641

# Comparison of water desalination performance of porous graphene and MoS<sub>2</sub> nanosheets†

Zailing Song,<sup>‡a</sup> Yunlong Niu,<sup>‡bc</sup> Juan Yang,<sup>a</sup> Liang Chen<sup>IDa</sup> and Junlang Chen<sup>ID\*a</sup>

Following graphene and its derivatives, molybdenum disulfide (MoS<sub>2</sub>) has become a research hotspot in two-dimensional materials. Both graphene and MoS<sub>2</sub> exhibit great potential in water treatment. A variety of nanoporous graphene or MoS<sub>2</sub> membranes have been designed for water desalination. In this work, we compared the water flux and ion rejection of MoS<sub>2</sub> and graphene nanopores, using molecular dynamics simulations. The simulation results demonstrate that monolayer nanopores have higher water fluxes than bilayer nanopores with lower ion rejection rates. MoS<sub>2</sub> nanopores perform better than graphene in terms of water permeability. Exploration of the underlying mechanism indicates that the water molecules in the MoS<sub>2</sub> pores have faster velocity and higher mass density than those in the graphene pores, due to the outer hydrophobic and inner hydrophilic edges of MoS<sub>2</sub> pores. In addition, increasing the polarity of the pore edge causes a decrease in water flux while enhancement of ion rejection. Our findings may provide theoretical guidance for the design of MoS<sub>2</sub> membranes in water purification.

Received 22nd July 2022  
Accepted 21st September 2022

DOI: 10.1039/d2ra04544c

rsc.li/rsc-advances

## 1. Introduction

In recent years, two-dimensional (2D) materials have received extensive interest due to their outstanding electronic, mechanical and optical properties, and have exhibited great potential in various fields, such as supercapacitors, photocatalysis and biosensors.<sup>1–3</sup> Another important application is in water treatment, since laminar 2D materials can be stacked into membranes as filters, or nanopores drilled on 2D materials allow water transport while reject the passage of ions.<sup>4–8</sup> Compared with conventional reverse osmosis (RO) membranes, which suffer from weak water permeation and high energy consumption, the filter membranes prepared from 2D materials often possess better desalination performance, including high water permeation, high ion rejection and cost-effectiveness.<sup>9</sup>

One kind of typical 2D material is graphene and its derivatives that have shown increasing potential in water desalination.<sup>10–15</sup> For example, Suk *et al.* first designed nanoporous graphene to transport water molecules *via* molecular dynamics (MD)

simulations. They found that the water flux of graphene membrane was higher than that of carbon nanotube for larger diameter pores.<sup>16</sup> Similarly, Cohen-Tanugi *et al.* introduced nanopores into graphene to filter salts. They studied the effects of pore size, edge modification and exerted pressure on the desalination performance of this freestanding graphene membrane using MD simulations.<sup>17</sup> Their results indicated that the water flux of the nanoporous graphene is 3–4 orders of magnitude higher than commercial RO membranes. Furthermore, graphene can be oxidized into graphene oxide (GO). And GO suspension can be formed into membranes through drop-casting or vacuum filtration, and so on.<sup>10,18</sup> The low cost and easy preparation of GO films have attracted much attention and have been extensively studied. GO membranes possess high water permeation and excellent ion rejection.<sup>19–21</sup> The unoxidized regions of the GO nanosheets provide an almost frictionless surface for the flow of water with high water permeability.<sup>22–24</sup> However, their use is limited by the swelling effect in aqueous solutions,<sup>25</sup> and the transport of water is low due to side-pinning effect between water and functional groups on the GO surface.<sup>26–28</sup> One method employed to inhibit swelling effect is reduction that GO is reduced to a certain extent to weaken its hydrophilicity. Another strategy to alleviate swelling effect is crosslinking.<sup>29,30</sup> For example, Huang *et al.* prepared a reduced GO (rGO) membrane that has low ion permeation and ideal water flux.<sup>31</sup> After GO sheets were crosslinked by urea, the performance of GO membranes was greatly improved that the rejection rates for MgSO<sub>4</sub> and CuSO<sub>4</sub> rose to 73.5% and 81.9%, respectively. In addition, low water permeation may be caused because of the distinct decrease in the interlayer spacing of GO membranes after reduction.<sup>32</sup>

<sup>a</sup>Department of Optical Engineering, College of Optical, Mechanical and Electrical Engineering, Zhejiang A&F University, Lin'an 311300, China. E-mail: chenjunlang7955@sina.com

<sup>b</sup>The State Key Laboratory of Industry Control Technology, College of Control Science and Engineering, Hangzhou 310027, China

<sup>c</sup>Radiation Monitoring Technical Center of Ministry of Ecology and Environment, State Environmental Protection Key Laboratory of Radiation Monitoring, Hangzhou 310012, China

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2ra04544c>

‡ These authors contributed equally to this work.



As a newly developed 2D material, molybdenum disulfide ( $\text{MoS}_2$ ) has attracted growing attention since its potential application in water treatment.<sup>33–39</sup> Li *et al.* prepared  $\text{MoS}_2$  membranes with a thickness of  $\sim 7$  nm for water desalination using chemical vapor deposition. These membranes owned both high water permeability ( $>322 \text{ L m}^{-2} \text{ h}^{-1} \text{ bar}^{-1}$ ) and high ion rejection capacity for  $\text{Na}^+$ ,  $\text{K}^+$ ,  $\text{Ca}^{2+}$ , and  $\text{Mg}^{2+}$  ( $>99\%$ ).<sup>35</sup> These prominent desalination performances are attributed to the intrinsic atomic vacancies between  $\text{MoS}_2$  layers. Another method to fabricate few-layer  $\text{MoS}_2$  is liquid-phase exfoliation. The obtained  $\text{MoS}_2$  thin film nanocomposite showed an optimal water permeability of  $6.2 \text{ L m}^{-2} \text{ h}^{-1} \text{ bar}^{-1}$  and salt rejection of 98.6% for  $\text{NaCl}$ .<sup>36</sup> Theoretically, Li *et al.* developed a tunable nanopore on a  $\text{MoS}_2$  nanosheet using MD simulations. By applying lateral strain, the nanopore can exhibit the “open” state allowing water transportation and impeding ion flow and “closed” state that both water and ions cannot pass through the pore.<sup>18</sup> Heiranian *et al.* performed MD simulations to investigate the water desalination performance of  $\text{MoS}_2$  nanopores. The pore areas fell in the range of  $20\text{--}60 \text{ \AA}^2$ . They constructed three kinds of  $\text{MoS}_2$  nanopores, namely, Mo atoms only, S atoms only and mixed Mo, S atoms on the pore edge. They found that Mo only pore has the highest rate of water permeation, because Mo only pore is much hydrophilic.<sup>37</sup> Using MD simulations, Kou *et al.* constructed a nanoporous  $\text{MoS}_2$  monolayer with different pore diameters ranging from  $5.3 \text{ \AA}$  to  $13.5 \text{ \AA}$ . They demonstrated that a nanoporous  $\text{MoS}_2$  membrane with a pore diameter of  $7.4 \text{ \AA}$  possesses both high water permeability and perfect salt rejection. The fast movement of water molecules across the monolayer  $\text{MoS}_2$  nanopore was attributed to the single-chain hydrogen bonds linking the water molecules inside and outside the nanopores.<sup>38</sup> Similarly, Azamat *et al.* designed four  $\text{MoS}_2$  nanopores with different areas ( $9.306\text{--}37.345 \text{ \AA}^2$ ) to filter heavy metal ions. They suggested that the most appropriate pore area for complete heavy metal rejection along with high water permeability is  $22.423 \text{ \AA}^2$ .<sup>39</sup>

Although both graphene and  $\text{MoS}_2$  monolayers possess excellent water desalination performance and theoretical studies show that  $\text{MoS}_2$  is better than graphene,<sup>40</sup> the comparison of desalination performance of these membranes needs further confirmation. On the other hand, multilayer membranes are more feasible and reasonable than monolayer


membranes in practical applications. In this work, we used MD simulations to investigate the water desalination performance of  $\text{MoS}_2$  and graphene nanopores in monolayer and bilayer membranes. Through varying the pore area, we determine an ideal pore size with high water permeation and reasonable ion rejection. Then, we compare the desalination performance of graphene and  $\text{MoS}_2$  nanopores under the applied pressures from 100 MPa to 300 MPa. And the fundamental mechanism is explored based on the analysis of water density and velocity in the pores.

## 2. Methods

Fig. 1(a) shows the configuration of an individual simulation system, which consists of four parts from left to right: a graphene piston,  $1 \text{ mol L}^{-1}$   $\text{NaCl}$  solution, a free-standing membrane with a nanopore and fresh water. The size of simulation box is  $4 \text{ nm} \times 4 \text{ nm} \times 13 \text{ nm}$ . The membranes used in the simulations were established by visual molecular dynamics (VMD) and Materials Studio (MS).<sup>41</sup> We constructed four types of membranes, namely,  $\text{MoS}_2$  monolayer,  $\text{MoS}_2$  bilayer, graphene (GE) monolayer and graphene bilayer, which are denoted as  $\text{MoS}_2$ ,  $\text{BiMoS}_2$ , GE and  $\text{BiGE}$ , respectively (Fig. 1(b)). The atoms at the center of the nanosheets were removed to obtain four pore sizes ( $47 \text{ \AA}^2$ ,  $56 \text{ \AA}^2$ ,  $64 \text{ \AA}^2$  and  $72 \text{ \AA}^2$ ).

All MD simulations were carried out by LAMMPS software.<sup>42</sup> Water molecules were realized by the SPC/E model.<sup>43</sup> The bonds and angles of water molecules were constrained by the SHAKE algorithm with the accuracy tolerance of 0.0001. The atomic interactions were calculated using the Lennard–Jones (LJ) potential as well as long-range Coulomb interactions. The LJ parameters of all atoms in the simulations were recorded in the ESI (see Table S1†). Arithmetic mix rule was adopted for interactions between different atoms. The cutoff radius of both LJ potential and Coulomb interaction was  $12 \text{ \AA}$ . The long-range Coulomb interaction was computed by the particle–particle mesh (PPPM) solver,<sup>44</sup> and the relative root mean square error was 0.005.

Each independent simulation consists of three steps: minimization, NPT ensemble relaxation, and NVT ensemble product simulation. First, 10 000 steps of iteration were performed to minimize the energy. Then, the NPT ensemble relaxation

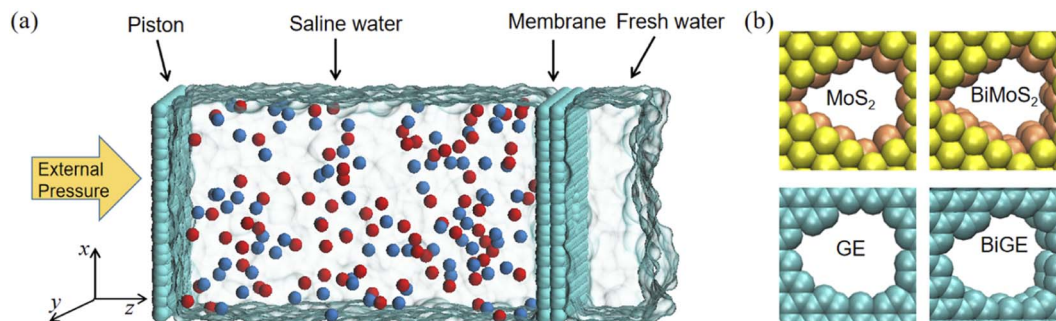

**Fig. 1** (a) Side view of an individual simulation system, composed of a piston, a membrane with a nanopore and two water boxes. The left water box is saline while the right one is fresh water. (b) Atomic structures of four nanopores. Color scheme: Mo yellow, S brown, C cyan,  $\text{Na}^+$  red and  $\text{Cl}^-$  blue.



process was conducted for 100 ps with a time step of 1 fs. The temperature was kept stable at 300 K and the pressure was controlled anisotropically at 1 bar by the Nosé–Hoover thermostat and barostat, respectively.<sup>45,46</sup> During equilibrium, the atoms of graphene and MoS<sub>2</sub> remained fixed, and the NPT process enabled water to reach the equilibrium density of water (1 g cm<sup>-3</sup>). Finally, the production run in NVT ensemble was carried out for 10 ns at 300 K with a time step of 2 fs. The external pressure was achieved by exerting forces on each atom of the piston. The force ( $f$ ) was determined by the following formula:

$$f = pS/N$$

where  $p$  is external pressure and  $S$  is the area of piston and  $N$  is the number of atoms of the piston.

### 3. Results and discussion

#### 3.1. Adsorption performance of graphene and MoS<sub>2</sub> nanosheets

Ahead of investigating water desalination through porous graphene and MoS<sub>2</sub> nanosheets, we should compare the adsorption features of water molecules on graphene and MoS<sub>2</sub> surface. Therefore, we first performed simulations of water with GE or MoS<sub>2</sub> monolayer or bilayer (see Fig. 2(a) and (b)). Fig. 2(c) shows the mass density of water on the four membranes. Similar to our previous study, we find that there are two adsorbed layers on membrane surface.<sup>47</sup> The first peaks of GE and BiGE are located at the same position ( $z = 0.40$  Å), close to the vdW radius of carbon atom. The corresponding mass density at this distance is 3.23 g cm<sup>-3</sup> and 3.85 g cm<sup>-3</sup>. Obviously, the mass density of water on BiGE is slightly higher than on GE. This is because the second GE monolayer enhances the adsorption. As comparison, the first peaks of MoS<sub>2</sub> and BiMoS<sub>2</sub> exhibit much lower than those of GE and BiGE, which is attributed to the atomic structure of MoS<sub>2</sub>. Interestingly, it is found that both peaks of MoS<sub>2</sub> and BiMoS<sub>2</sub> are completely overlapped ( $\sim 2.46$  g cm<sup>-3</sup>). That is, the adsorption capacities of MoS<sub>2</sub> and BiMoS<sub>2</sub> are almost identical. The thicknesses of MoS<sub>2</sub> monolayer and bilayer are approximately 6.2 Å and 12.4 Å,<sup>48</sup> therefore, the interactions between water molecules and the second MoS<sub>2</sub> layer are almost negligible, as the distance between water molecules and the

second MoS<sub>2</sub> layer is approximate 10 Å, which is close to the cutoff of vdW interactions. This indicates that the graphene surface is more hydrophilic than MoS<sub>2</sub> (S site).<sup>29</sup> Correspondingly, water molecules in the first adsorbed layer are thermodynamically stable, especially on GE surface.

#### 3.2. Determining the optimal pore size of the four membranes

In general, water flux is directly proportional to pore size, while ion rejection is inversely proportional to pore size.<sup>49</sup> Therefore, we should make a compromise between water flux and ion rejection. In detail, we should try to improve the water permeability as well as acceptable ion rejection. We varied the pore area from 47 Å<sup>2</sup> to 72 Å<sup>2</sup> to find a reasonable pore size for this purpose. Fig. 3 presents the water desalination performance of the four membranes with different pore area at external pressure of 150 MPa. It is found that the intersection points between water flux and ion rejection are close with each other at  $\sim 62$  Å<sup>2</sup> in all four cases. Since pore area is not continuous but discrete with the number of removed atoms, we conclude that the pore area at 64 Å<sup>2</sup> is an optimal size suitable to water desalination. At this point, the four membranes achieve a reasonable balance between water permeation and ion rejection. The water fluxes are 96.67 ns<sup>-1</sup>, 78.37 ns<sup>-1</sup>, 71.43 ns<sup>-1</sup>, 65.93 ns<sup>-1</sup>, and the rejection rates are 94.41%, 98.33%, 95.53%, 98.23% for MoS<sub>2</sub>, BiMoS<sub>2</sub>, GE, BiGE, respectively. The water desalination performance of the four membranes with different pore area at external pressure of 200 MPa holds the similar trend (see ESI, Fig. S1†). In the following comparison of desalination performance of the four membranes, pore area is fixed at this value (64 Å<sup>2</sup>).

#### 3.3. Comparing the water flux and ion rejection of the four membranes

As shown in Fig. 4(a), the water flux ratchets up gradually with the increasing pressure. MoS<sub>2</sub> pore has the highest water flux followed by BiMoS<sub>2</sub>, GE and BiGE for all the applied pressures from 100 MPa to 300 MPa. On the other hand, the monolayer provides a higher flux than bilayer. For example, the water fluxes of MoS<sub>2</sub> and BiMoS<sub>2</sub> are 96.67 ns<sup>-1</sup> and 78.36 ns<sup>-1</sup> at the external pressure of 150 MPa (see ESI, Fig. S2(e)†). Particularly, MoS<sub>2</sub> nanopores own higher water permeance than GE

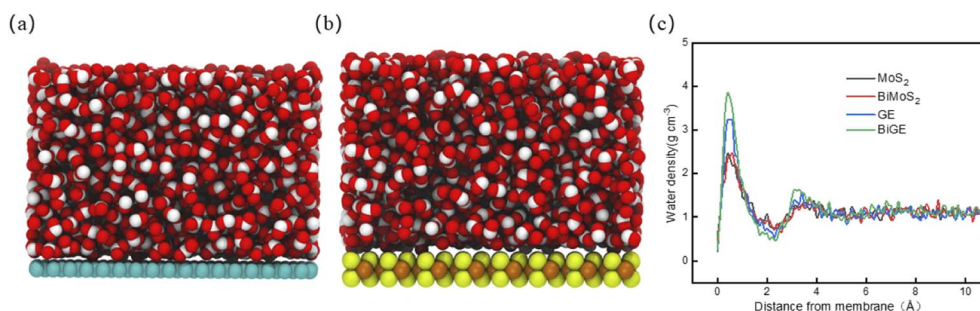


Fig. 2 (a) Snapshot of water on GE surface. (b) Snapshot of water on MoS<sub>2</sub> surface. (c) Mass density profiles of water molecules with the distance from nanosheets.



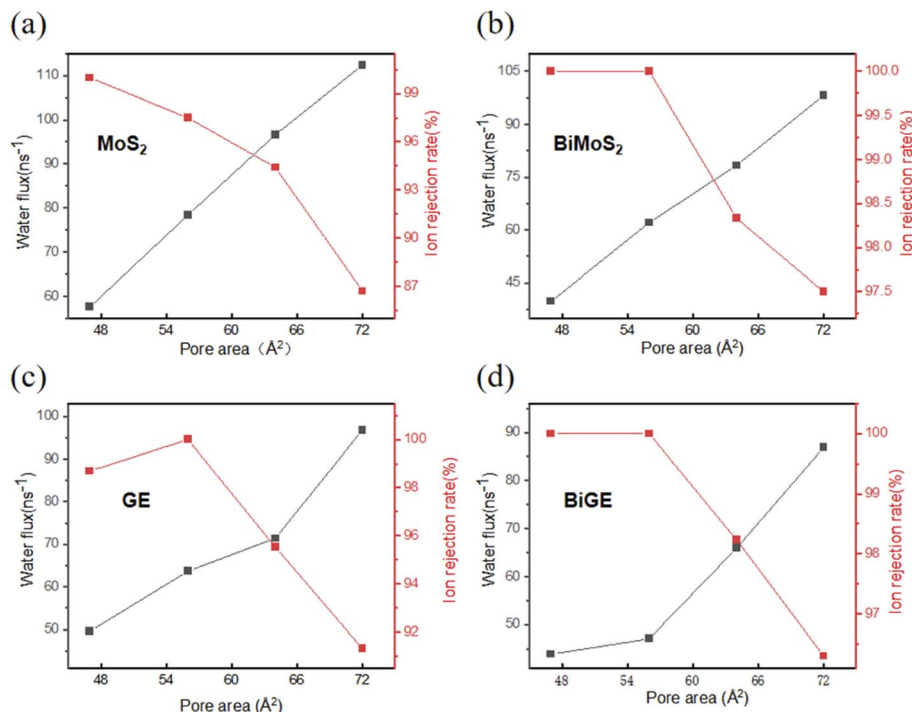


Fig. 3 Water flux and ion rejection against pore size of four membranes. (a)  $\text{MoS}_2$  monolayer, (b)  $\text{MoS}_2$  bilayer, (c) GE monolayer, (d) GE bilayer.

nanopores regardless of monolayer or bilayer. For example, the water flux of  $\text{MoS}_2$  nanopore is approximate  $96.67 \text{ ns}^{-1}$ , while this flux decline to  $71.43 \text{ ns}^{-1}$  for GE nanopore (Fig. S2(e)†) at 150 MPa.  $\text{MoS}_2$  monolayer and bilayer perform 35.4% and 18.9% better than its GE counterparts at this external pressure. The water flux of  $\text{MoS}_2$  and GE under other pressures presents the similar results (see ESI, Fig. S2†). Another important parameter in water desalination is ion rejection rate, which indicates the capacity of the membrane to filter ions. Fig. 4(b) presents the percentage of ions blocked by the four nanopores. In general, the ion rejection decreases with the increasing pressures as high pressures exert higher forces on the ions leading to more ions passing the pores. For example, the ion rejection of  $\text{MoS}_2$  nanopore declines from 95.43% to 70.36% with the pressure increasing from 100 MPa to 300 MPa. Contrary to the water flux, monolayer has a lower ion rejection

than bilayer. Taking  $\text{MoS}_2$  and  $\text{BiMoS}_2$  at 100 MPa as an example, the rejection rate of  $\text{MoS}_2$  is 95.43%, while that of  $\text{BiMoS}_2$  reaches highly 99.13%. This is because bilayer membranes increase the length of the channel, thereby enhancing the resistance of ions to pass through. Unfortunately,  $\text{MoS}_2$  nanopore exhibits the lowest ion rejection at the same pressure, especially at higher pressure. Fig. S2(f)† shows the number of ions passing the pore as a function of simulation time. During the 10 ns simulation, approximate 7, 2, 5 and 2  $\text{Na}^+$  ions go through the  $\text{MoS}_2$ ,  $\text{BiMoS}_2$ , GE and  $\text{BiGE}$  pores, respectively. Although  $\text{MoS}_2$  nanopore has high ion permeation, the rejection rates at pressure <150 MPa are still higher than 95%.

### 3.4. Velocity and density of water in the pores

In order to further understand the fundamental physics of the water flux difference between of  $\text{MoS}_2$  and GE nanopores, we

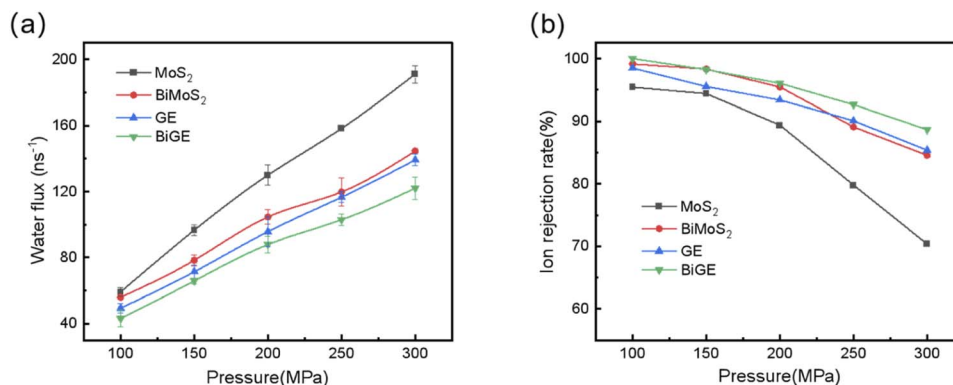


Fig. 4 (a) Water flux and (b) ion rejection rate as a function of the exerted pressure for the four nanopores.





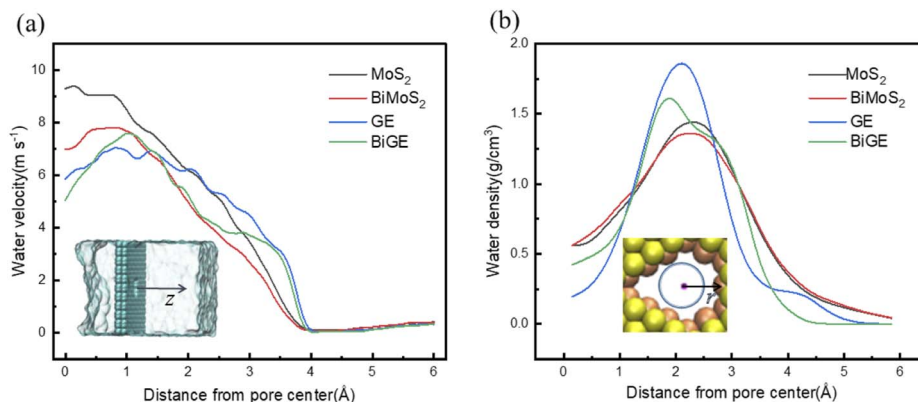


Fig. 5 (a) Axial velocity of water molecules in z-direction for the four nanopores. (b) Mass density profiles of water molecules in the four pores along the radial direction (xy-plane). The insets illustrate the distance from pore center along the axes.

depict the velocity and mass density profiles of water molecules in the pores for four nanosheets, taking 200 MPa as an example. As shown in Fig. 5(a), the axial velocities are higher in MoS<sub>2</sub> pores center compared with GE pores regardless of monolayer and bilayer. The average velocities of water molecules in the pore center are 9.30, 6.98, 5.85 and 5.06 ms<sup>-1</sup>, respectively. This is determined by the nature of the pores, as MoS<sub>2</sub> nanopores (Mo atoms on the pore edge) are more hydrophilic than GE nanopores. Another important reason is that the adsorption intensity of GE is stronger than that of MoS<sub>2</sub>, therefore, water molecules on the adsorption layer on GE surface is more difficult to flow towards the pore. On the other hand, the velocities are higher in monolayer than those in bilayer, since there are interlayer gaps in bilayer that takes water molecules more time to pass through. Fig. 5(b) shows the density profiles of water molecules in the pores. It can be seen that although GE and BiGE have higher peaks, the peaks are very narrow. As comparison, MoS<sub>2</sub> nanosheets have lower peaks than graphene. However, the density profiles of water in MoS<sub>2</sub> nanopores is much wide and uniform, since MoS<sub>2</sub> nanosheets have longer channels to accommodate more water molecules. Finally, we averaged the water densities of the four membranes (MoS<sub>2</sub>, BiMoS<sub>2</sub>, GE, BiGE) that were 0.67 g cm<sup>-3</sup>, 0.68 g cm<sup>-3</sup>, 0.61 g cm<sup>-3</sup>, 0.61 g cm<sup>-3</sup>. In general, water molecules have

higher speed and density when passing through the MoS<sub>2</sub> membrane, which leads to a higher water flux than GE membranes.

### 3.5. Effects of pore charge on water flux and ion rejection of BiMoS<sub>2</sub> membrane

Eventually, we explored the effects of pore charge on water flux and ion rejection of BiMoS<sub>2</sub> membrane. We varied the charges of Mo atoms on pore edge from 0 to 0.6 e. Correspondingly, the charges of S atoms are half of those of Mo atoms. The results were presented in Fig. 6. It can be seen that the water flux decreases rapidly with the increase of the charges of MoS<sub>2</sub> on the pore edge. For example, the water fluxes are 78.46, 35.40, 21.63 and 12.95 ns<sup>-1</sup> at 150 MPa, when the charges of Mo are 0, 0.2, 0.4 and 0.6 e. That is, the increase of the polarity of pore edge causes the decrease of water flux, which is attributed to the polar interactions between MoS<sub>2</sub> and water molecules. On the contrary, the polarity of MoS<sub>2</sub> on the pore edge play a positive role in ion rejection. Similarly, taking rejection rate at 150 MPa as an example, we found that the ion rejection rates are almost 100%, when the charges of Mo atoms on the pore edge are 0.2, 0.4 and 0.6 e. Even if the external pressure increases to 300 MPa, the ion rejection rates are 98.7%, 98.7% and 99.4%, when the charges of Mo atoms are 0.2, 0.4 and 0.6 e. However, the ion

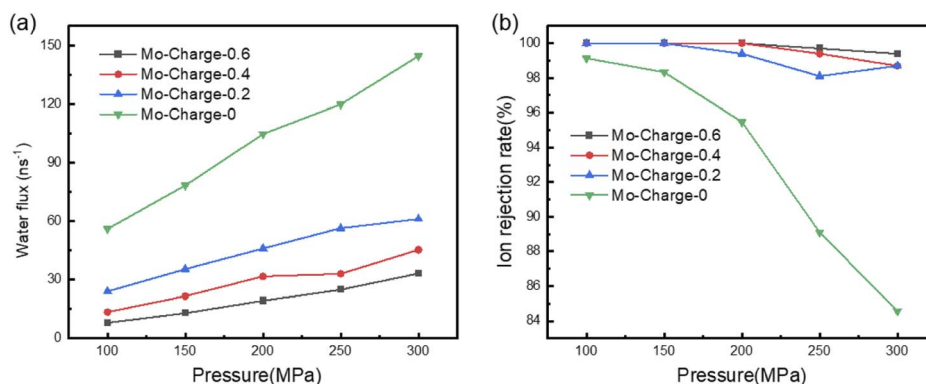


Fig. 6 BiMoS<sub>2</sub> water flux and ion repulsion for different charges. (a) Water flux and (b) ion repulsion rate as a function of applied pressure of BiMoS<sub>2</sub> nanopores.

rejection rate falls sharply to 84.6% if the atoms on pore edge are uncharged. As a result, increasing the pore charge enhances the ion rejection.

## 4. Conclusions

Using MD simulations, we have compared the water flux and ion rejection of MoS<sub>2</sub> monolayer, MoS<sub>2</sub> bilayer, graphene monolayer and graphene bilayer with pore area ranging from 47 Å<sup>2</sup> to 72 Å<sup>2</sup>. The results show that (1) the water flux of MoS<sub>2</sub> is higher than that of graphene with similar pore area regardless of monolayer or bilayer; (2) monolayer has higher water flux than bilayer; (3) on the contrary, monolayer has lower ion rejection than bilayer. On the other hand, increasing pore area or applied pressure leads to higher water permeability but with lower ion rejection. Considering that the membranes prepared in the experiments are often multi-layered, we propose that MoS<sub>2</sub> bilayer with pore area of 64 Å<sup>2</sup> is most suitable for water desalination. In addition, increasing the polarity of pore edge play a negative role in water flux but a positive role in ion rejection.

## Conflicts of interest

The authors declare no competing financial interests.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (Grant No. 11875236, 12075212, 12105246), the Zhejiang Provincial Natural Science Foundation of China (Grant No. LY22A040008).

## References

- 1 M. A. Shannon, P. W. Bohn, M. Elimelech, J. G. Georgiadis, B. J. Mariñas and A. M. Mayes, *Nature*, 2008, **452**, 301–310.
- 2 D. Cohen-Tanugi, R. K. McGovern, S. H. Dave, J. H. Lienhard and J. C. Grossman, *Energy Environ. Sci.*, 2014, **7**, 1134–1141.
- 3 L. Wang, M. S. H. Boutilier, P. R. Kidambi, D. Jang, N. G. Hadjiconstantinou and R. Karnik, *Nat. Nanotechnol.*, 2017, **12**, 509–522.
- 4 L. Sun, Y. Ying, H. Huang, Z. Song, Y. Mao, Z. Xu and X. Peng, *ACS Nano*, 2014, **8**, 6304–6311.
- 5 S. Qin, D. Liu, G. Wang, D. Portehault, C. J. Garvey, Y. Gogotsi, W. Lei and Y. Chen, *J. Am. Chem. Soc.*, 2017, **139**, 6314–6320.
- 6 C. E. Ren, K. B. Hatzell, M. Alhabeb, Z. Ling, K. A. Mahmoud and Y. Gogotsi, *J. Phys. Chem. Lett.*, 2015, **6**, 4026–4031.
- 7 D. Jiang, V. R. Cooper and S. Dai, *Nano Lett.*, 2009, **9**, 4019–4024.
- 8 Z. Cao, V. Liu and A. Barati Farimani, *ACS Energy Lett.*, 2020, **5**, 2217–2222.
- 9 S. S. Shenvi, A. M. Isloor and A. F. Ismail, *Desalination*, 2015, **368**, 10–26.
- 10 S. P. Koenig, L. Wang, J. Pellegrino and J. S. Bunch, *Nat. Nanotechnol.*, 2012, **7**, 728–732.
- 11 S. P. Surwade, S. N. Smirnov, I. V. Vlassiuk, R. R. Unocic, G. M. Veith, S. Dai and S. M. Mahurin, *Nat. Nanotechnol.*, 2015, **10**, 459–464.
- 12 Z. Song and Z. Xu, *Sci. Rep.*, 2015, **5**, 10597.
- 13 D. Jiang, V. R. Cooper and S. Dai, *Nano Lett.*, 2009, **9**, 4019–4024.
- 14 K. Celebi, J. Buchheim, R. M. Wyss, A. Droudian, P. Gasser, I. Shorubalko, J.-I. Kye, C. Lee and H. G. Park, *Science*, 2014, **344**, 289–292.
- 15 Q. Xu, H. Xu, J. Chen, Y. Lv, C. Dong and T. S. Sreeprasad, *Inorg. Chem. Front.*, 2015, **2**, 417–424.
- 16 M. E. Suk and N. R. Aluru, *J. Phys. Chem. Lett.*, 2010, **1**, 1590–1594.
- 17 D. Cohen-Tanugi, L.-C. Lin and J. C. Grossman, *Nano Lett.*, 2016, **16**, 1027–1033.
- 18 W. Li, Y. Yang, J. K. Weber, G. Zhang and R. Zhou, *ACS Nano*, 2016, **10**, 1829–1835.
- 19 R. K. Joshi, P. Carbone, F. C. Wang, V. G. Kravets, Y. Su, I. V. Grigorieva, H. A. Wu, A. K. Geim and R. R. Nair, *Science*, 2014, **343**, 752–754.
- 20 R. R. Nair, H. A. Wu, P. N. Jayaram, I. V. Grigorieva and A. K. Geim, *Science*, 2012, **335**, 442–444.
- 21 S. Zeng, Y. Ji, Y. Shen, R. Zhu, X. Wang, L. Chen and J. Chen, *RSC Adv.*, 2020, **10**, 8744–8750.
- 22 S. Kumar Kannam, B. D. Todd, J. S. Hansen and P. J. Daivis, *Chem. Phys.*, 2012, **136**, 024705.
- 23 M. C. Gordillo and J. Martí, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 075432.
- 24 J. Martí, J. Sala and E. Guàrdia, *J. Mol. Liq.*, 2010, **153**, 72–78.
- 25 S. Zheng, Q. Tu, J. J. Urban, S. Li and B. Mi, *ACS Nano*, 2017, **11**, 6440–6450.
- 26 C.-N. Yeh, K. Raidongia, J. Shao, Q.-H. Yang and J. Huang, *Nat. Chem.*, 2015, **7**, 166–170.
- 27 H. Huang, Y. Mao, Y. Ying, Y. Liu, L. Sun and X. Peng, *Chem. Commun.*, 2013, **49**, 5963.
- 28 L. S. Melro, R. Pyrz and L. R. Jensen, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2016, **139**, 012036.
- 29 M. Hu and B. Mi, *Environ. Sci. Technol.*, 2013, **47**, 3715–3723.
- 30 H. Liu, H. Wang and X. Zhang, *Adv. Mater.*, 2015, **27**, 249–254.
- 31 H.-H. Huang, R. K. Joshi, K. K. H. De Silva, R. Badam and M. Yoshimura, *J. Membr. Sci.*, 2019, **572**, 12–19.
- 32 Y. Zhang, K. Su and Z. Li, *J. Membr. Sci.*, 2018, **563**, 718–725.
- 33 L. Sun, H. Huang and X. Peng, *Chem. Commun.*, 2013, **49**, 10718.
- 34 J. Feng, M. Graf, K. Liu, D. Ovchinnikov, D. Dumcenco, M. Heiranian, V. Nandigana, N. R. Aluru, A. Kis and A. Radenovic, *Nature*, 2016, **536**, 197–200.
- 35 H. Li, T.-J. Ko, M. Lee, H.-S. Chung, S. S. Han, K. H. Oh, A. Sadmani, H. Kang and Y. Jung, *Nano Lett.*, 2019, **19**, 5194–5204.
- 36 Y. Li, S. Yang, K. Zhang and B. Van der Bruggen, *Desalination*, 2019, **454**, 48–58.
- 37 M. Heiranian, A. B. Farimani and N. R. Aluru, *Nat. Commun.*, 2015, **6**, 8616.
- 38 J. Kou, J. Yao, L. Wu, X. Zhou, H. Lu, F. Wu and J. Fan, *Phys. Chem. Chem. Phys.*, 2016, **18**, 22210–22216.



- 39 J. Azamat and A. Khataee, *Comput. Mater. Sci.*, 2017, **137**, 201–207.
- 40 A. B. Farimani, K. Min and N. R. Aluru, *ACS Nano*, 2014, **8**, 7914–7922.
- 41 W. Humphrey, A. Dalke and K. Schulten, *J. Mol. Graphics*, 1996, **14**, 33–38.
- 42 S. Plimpton, *J. Comput. Phys.*, 1995, **117**, 1–19.
- 43 P. Mark and L. Nilsson, *J. Phys. Chem. A*, 2001, **105**, 9954–9960.
- 44 M. P. Allen and D. J. Tildesley, *Computer simulation of liquids*, Clarendon Press and Oxford University Press, Oxford, England and New York, 1987.
- 45 S. Nosé, *J. Chem. Phys.*, 1984, **81**, 511–519.
- 46 W. G. Hoover, *Phys. Rev. A*, 1985, **31**, 1695–1697.
- 47 Q. Tan, Y. Fan, Z. Song, J. Chen and L. Chen, *J. Mol. Model.*, 2022, **28**, 57.
- 48 Z. Wang, Q. Tu, S. Zheng, J. J. Urban, S. Li and B. Mi, *Nano Lett.*, 2017, **17**, 7289–7298.
- 49 S. Gravelle, L. Joly, F. Detcheverry, C. Ybert, C. Cottin-Bizonne and L. Bocquet, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 16367–16372.

