




Cite this: *RSC Adv.*, 2022, 12, 29003

# KMnCuTe<sub>2</sub>: a layered antiferromagnetic semiconductor with long metal–metal distance†

Fan Sun,<sup>a</sup> Zhao Liu,<sup>a</sup> Jiawei Lin,<sup>a</sup> Jun Deng,<sup>b</sup> Zhongnan Guo <sup>\*a</sup> and Wenxia Yuan <sup>\*a</sup>

The magnetic semiconductor in a two-dimensional system is a major subject for both theoretical and experimental investigations. Here we report the synthesis of a new quaternary manganese chalcogenide KMnCuTe<sub>2</sub>, which shows layered structure and antiferromagnetic (AFM) semiconducting features. Single crystals of KMnCuTe<sub>2</sub> were obtained using a self-flux method and based on single-crystal X-ray diffraction, KMnCuTe<sub>2</sub> adopts the ThCr<sub>2</sub>Si<sub>2</sub>-type structure composed of edge-sharing tetrahedral layers separated by K<sup>+</sup> cations. The Mn and Cu atoms randomly distribute in the centre of tetrahedral units. Attributed to the large radius of Te, KMnCuTe<sub>2</sub> has large lattice parameters ( $a = 4.3115(3)$  Å and  $c = 14.9360(20)$  Å), leading to a long metal–metal distance (3.049 Å) in the tetrahedral layers. Based on the experiments and theoretical calculations, KMnCuTe<sub>2</sub> exhibits a G-type AFM interaction with the transition temperature at around 225 K and an indirect semiconducting nature with the band gap of 0.95 eV. The magnetic semiconducting property of KMnCuTe<sub>2</sub> is unique in AMnMCh<sub>2</sub> systems (A = Li, Na, K, M = Cu, Ag and Ch = S, Se, Te), which could be associated with the large metal–metal distance. Our work not only highlights the role of metal–metal interactions on regulating the properties of ThCr<sub>2</sub>Si<sub>2</sub>-type compounds, but also provides a feasible strategy to obtain the layered magnetic semiconductor.

Received 31st July 2022  
Accepted 5th October 2022

DOI: 10.1039/d2ra04789f

rsc.li/rsc-advances

## Introduction

The ThCr<sub>2</sub>Si<sub>2</sub>-type structure is a very common one for ternary inorganic compounds. In the last decade, the transition metal chalcogenides with ThCr<sub>2</sub>Si<sub>2</sub>-type structure have attracted intense attention attributed to the discovery of Fe-based high-temperature superconductors.<sup>1–3</sup> From the crystal structure point of view, the ThCr<sub>2</sub>Si<sub>2</sub>-type iron chalcogenides are composed of edge-sharing FeCh<sub>4</sub> tetrahedral layers (Ch = S, Se, Te) with the alkali metal intercalated in between the layers.<sup>4</sup> Stimulated by the fascinating Fe-based ThCr<sub>2</sub>Si<sub>2</sub>-type compounds, the Ni- and Co-based analogues have also been fully investigated, and exhibit heavy-fermion behavior and long-range magnetic order, respectively.<sup>5–9</sup> Interestingly, the ThCr<sub>2</sub>-Si<sub>2</sub>-type structure can also be formed in transition metal chalcogenides by mixing the metal site in tetrahedral layers, largely

enriching the compositional diversity of this material family. In these “metal-mixed” phases, the transition metal ions are partially substituted by monovalent metal ions M<sup>+</sup>, forming a series of quaternary metal chalcogenides including AFEMCh<sub>2</sub>, ACoMCh<sub>2</sub>, AMnMCh<sub>2</sub>, ACrMCh<sub>2</sub> and AZnMCh<sub>2</sub> (A = K, Rb, Cs, M = Cu, Ag, Li and Ch = S, Se, Te).<sup>10–24</sup> Recently, the alkaline-earth metal chalcogenides KMgCuSe<sub>2</sub> and KMgCuTe<sub>2</sub> with ThCr<sub>2</sub>Si<sub>2</sub>-type structure were also synthesized by our group.<sup>25</sup> Given the similar chemical composition with the Fe-based high-temperature superconductors, the KFeAgTe<sub>2</sub> was described in more details focusing on the interactions between its crystal structure, magnetic order and electronic structure.<sup>12,13,26</sup> Very recently, the intertwined magnetic order and nematic orders, which were considered as the feature of Fe-based high-temperature superconductors, were observed in KFeAgTe<sub>2</sub>.<sup>27</sup> A exotic spin-nematic state induced by a small strain was also observed in this layered iron telluride.<sup>28</sup>

The layered manganese chalcogenide AMnMCh<sub>2</sub> (A = K, Rb, Cs, M = Cu, Ag and Ch = S, Se, Te) are also intriguing materials, not only as a similar specimen to Fe-based superconductors in electronic structure but also as a potential two-dimensional (2D) magnetic system. It was reported that some members in AMnMCh<sub>2</sub> family show the spin-glass state while the others are paramagnets.<sup>16–18</sup> However, the long-range magnetic order such as antiferromagnetic (AFM) interaction has not been reported yet in this Mn-based quaternary family. It has been revealed that the lattice parameters, especially the metal–metal distances in

<sup>a</sup>Department of Chemistry, School of Chemistry and Biological Engineering, University of Science and Technology Beijing, Beijing, 100083, China. E-mail: guozhongn@ustb.edu.cn; wxyuanwz@163.com

<sup>b</sup>Research & Development Centre for Functional Crystals, Beijing National Laboratory for Condensed Matter Physics, Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China

† Electronic supplementary information (ESI) available: Crystal data, atomic coordinates, displacement parameters and anisotropic displacement parameters of KMnCuTe<sub>2</sub> (Tables S1–S3) and PXRD patterns in Fig. S1. CCDC 2193743. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2ra04789f>



*ab* plane, play a key role on determining the magnetism and transport properties for  $\text{ThCr}_2\text{Si}_2$ -type materials.<sup>18,22</sup> Synthesizing the new member in  $\text{AMnMCh}_2$  family with large metal-metal distance could be expected to realize the unique physical property.

In this work, we report the single-crystal growth of a new member in  $\text{AMnMCh}_2$  family,  $\text{KMnCuTe}_2$ . It is indicated that the title compound adopts the  $\text{ThCr}_2\text{Si}_2$ -type structure that is comprised of edge-sharing  $[\text{Mn}(\text{Cu})\text{Te}_4]$  tetrahedral layers with intercalated  $\text{K}^+$  cations. The Mn and Cu atoms randomly distribute in the centre of tetrahedron with the ratio of Mn : Cu close to 1 : 1 due to the similar radii of Mn and Cu. Due to the large radius of Te,  $\text{KMnCuTe}_2$  has much larger lattice parameters ( $a = 4.3115(3)$  Å and  $c = 14.9360(20)$  Å) compared to the sulfides and selenides in  $\text{AMnMCh}_2$ , leading to a long metal-metal distance in tetrahedral layers (3.049 Å). Based on the experiments and theoretical calculations, we demonstrate that  $\text{KMnCuTe}_2$  exhibits unique magnetic semiconducting behavior with an indirect band gap (0.95 eV) and G-type AFM interaction.

## Experimental section

### Synthesis

Single-crystals of  $\text{KMnCuTe}_2$  were grown by self-flux method. Powders of Mn (99.99%, Aladdin), Cu (99.9%, Aladdin) and Te (99.9%, Aladdin) were mixed with 1 : 1 : 2 molar ratio and ground in an agate mortar. The raw materials were cold-pressed into disks with 10 mm diameter under  $200 \text{ kg cm}^{-2}$  uniaxial stress and put into the alumina crucibles together with K ingot (97%, SINOPHARM) as predetermined compositions. The total mass of the samples was around 2 g. The alumina crucibles were sealed into the quartz tubes under vacuum and then firstly heated to 473 K and held for 12 hours for the pre-reaction of potassium and Te. After pre-reaction, the samples were re-ground and cold-pressed again. All the manipulations were carried out inside an argon-filled glove box ( $\text{O}_2 < 1$  ppm) in order to prevent the sample oxidation. The disks were heated to 1273 K in 12 hours, held for 48 hours, and then cooled down to 874 K with the cooling rate of 4 K per hour before cooling to room temperature. It should be mentioned that the crucibles was shook for several times during the heating process of synthesis to obtain the homogeneous phase.

### Characterization

Powder X-ray diffraction (PXRD) were collected on a PANalytical diffractometer (X'Pert PRO MRD) equipped with Cu  $\text{K}\alpha$  radiation ( $\lambda = 1.5406$  Å) operation at 40 kV and 40 mA. Single crystal X-ray diffraction (SCXRD) was performed on a Bruker D8 Venture diffractometer at 50 kV and 1.4 mA with Mo  $\text{K}\alpha$  radiation ( $\lambda = 0.71073$  Å). All data were collected at room temperature under nitrogen flow. The crystal structure of  $\text{KMnCuTe}_2$  was solved (using direct method) and refined using Jana 2006 package.<sup>29</sup> Morphology of the samples was investigated *via* scanning electron microscopy (SEM, Hitachi S-4800), and the component analysis was made by energy dispersive X-ray spectroscopy (EDS). The result for each sample was obtained based

on the average of 10 sets of data. The magnetization susceptibility was measured using a vibrating sample magnetometer (VSM, Quantum Design) from 300 to 10 K. The electrical resistivity of single crystal samples was measured *via* four-probe method using a physical property measurement system (PPMS, Quantum Design). The specific heat capacity was also measured using PPMS. The optical diffuse reflectance measurements were performed at room temperature using a Shimadzu UV-3600 UV-vis-NIR spectrometer and  $\text{BaSO}_4$  was used as the reference of 100% reflectance. The absorption data were calculated based on the obtained reflectance spectrum according to the Kubelka-Munk equation,  $\alpha/S = (1 - R)^2/(2R)$ , where  $R$  is the reflectance and  $\alpha$  and  $S$  are the absorption and scattering coefficients, respectively.<sup>30</sup>

### Calculation

All calculations were performed in the density functional theory (DFT) using Vienna *ab initio* simulation package (VASP), and the projector-augmented wave (PAW) scheme and Perdew-Burke-Ernzerhof generalized gradient approximation (PBE-GGA) were used for the exchange correlation functional.<sup>31-33</sup> The wave functions were expanded into plane-wave up to a cutoff energy of 450 eV.<sup>34</sup> We built a  $2 \times 2 \times 1$  supercell to simulate the different magnetic structures, and a Monkhorst-Pack  $k$ -mesh of  $4 \times 4 \times 2$  was used for sampling the first Brillouin zone in the self-consistent calculation.<sup>35</sup> The structures were relaxed with an energy convergence criterion of  $10^{-6}$  eV, ensuring that the maximum force on an atom was  $< 0.03 \text{ eV Å}^{-1}$ . Considering the strong correlations of 3d electrons of Cu and Mn, on-site Hubbard  $U$  for 3d orbitals with  $U = 5$  eV was adopted.<sup>36</sup>

## Results and discussion

We successfully synthesized a new quaternary manganese chalcogenide  $\text{KMnCuTe}_2$ , which is a new member in  $\text{AMnMCh}_2$  ( $A = \text{K, Rb, Cs}$ ,  $M = \text{Cu, Ag}$  and  $\text{Ch} = \text{S, Se, Te}$ ) family.<sup>16-18</sup> Using self-flux method, single crystal sheets were obtained by cleaving the crystal grains as shown in Fig. 1a, and the products show black color and are about 1 mm in size. Elemental mapping in Fig. 1b confirms the homogeneous distribution of K, Mn, Cu and Te in sample. Chemical analysis by EDS shows that the atomic ratio of K : Mn : Cu : Te is 0.97 : 0.96 : 0.98 : 2, which is close to the stoichiometry.

The single-crystal of  $\text{KMnCuTe}_2$  was picked directly from the product for SCXRD measurement. The obtained crystallographic information and structural parameters are listed in Tables S1-S3.† It can be seen that the final refinement gives very low weight agreement factors  $R_{\text{int}}$ ,  $R$  and  $R_w$ , suggesting that our structure solution is satisfactory.  $\text{KMnCuTe}_2$  crystallizes in the  $\text{ThCr}_2\text{Si}_2$ -type structure, which adopts a body-centered tetragonal lattice with the space group of  $I4/mmm$  (No. 139). The lattice parameters are refined to be  $a = 4.3115(3)$  Å and  $c = 14.9360(20)$  Å, comparable to the analogous tellurides including  $\text{KFeCuTe}_2$ ,  $\text{KFe}_{0.85}\text{Ag}_{1.15}\text{Te}_2$ ,  $\text{CsMn}_{1.18}\text{Ag}_{0.64}\text{Te}_2$  and  $\text{CsFe}_{0.72}\text{Ag}_{1.28}\text{Te}_2$ .<sup>12,20,23,24</sup> As shown in Fig. 1c, the structure shows very typical layered nature, which is composed of the edge-sharing



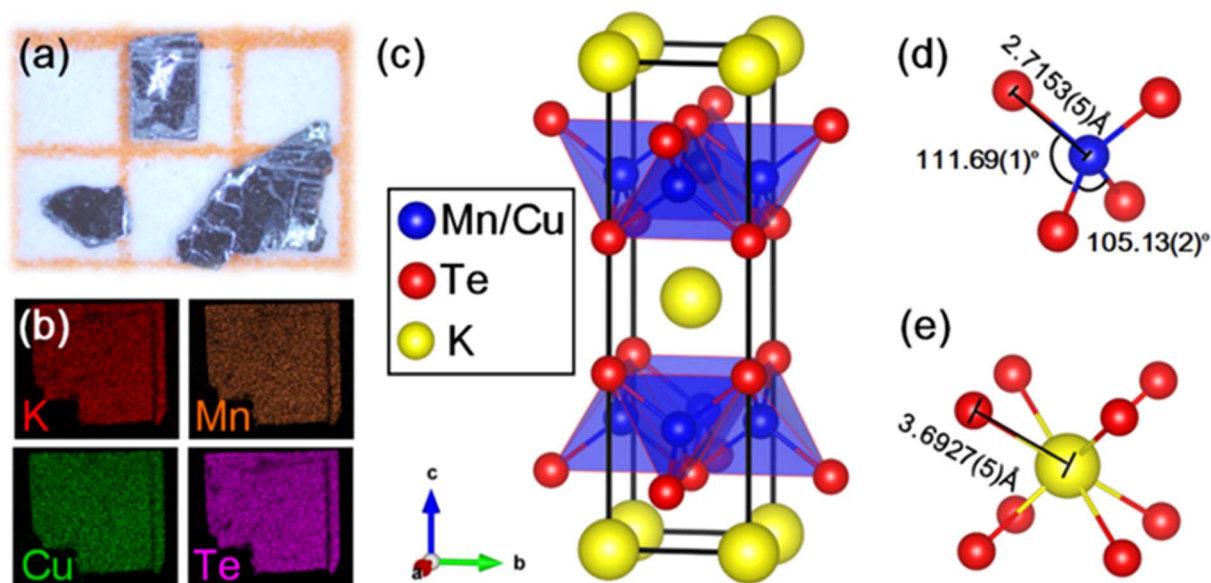


Fig. 1 (a) Optical photograph of the single-crystal sample of  $\text{KMnCuTe}_2$ . (b) Elemental mapping of the sample. (c) Crystal structure of  $\text{KMnCuTe}_2$  with tetragonal  $I4/mmm$  space group. The detailed bond lengths and angles in (d)  $[\text{Mn}(\text{Cu})\text{Te}_4]$  tetrahedron and (e)  $[\text{KTe}_8]$  cube.

$[\text{Mn}(\text{Cu})\text{Te}_4]$  tetrahedral layer extending in the  $ab$  plane and the potassium ions are located in the  $[\text{KTe}_8]$  cubic sites between the layers. The Mn and Cu atoms are randomly distributed in the centre of tetrahedral units (shown in Fig. 1c) and this mixed occupation is mainly due to the similar radii of Mn and Cu. The  $[\text{Mn}(\text{Cu})\text{Te}_4]$  tetrahedron is compressed along the  $ab$  plane with the four Te–Mn(Cu)–Te angles across the  $ab$  plane being  $111.69(1)^\circ$  and the other two Te–Mn(Cu)–Te angles on the same side being  $105.13(2)^\circ$ , as shown in Fig. 1d. The Mn(Cu)–Te bond length is refined as  $2.7153(5) \text{ \AA}$ , which is larger than Fe(Cu)–Te bond length ( $2.6344(8) \text{ \AA}$ ) in the analogue,  $\text{KFeCuTe}_2$ .<sup>20</sup> The distance between  $\text{K}^+$  and the neighboring  $\text{Te}^{2-}$  is  $3.6927(5) \text{ \AA}$  (Fig. 1e), implying the negligible interaction between the alkali metals and the transition telluride layers. The refined composition from SCXRD is  $\text{KMn}_{0.96}\text{Cu}_{1.04}\text{Te}_2$ , which is in good agreement with the EDS result. The PXRD pattern of the powder sample from grinding the crystals matches well with the simulated one from SCXRD, as shown in Fig. S1†. We found that  $\text{KMnCuTe}_2$  is chemically stable in ambient condition, with the PXRD pattern basically unchanged after exposure in air for 7 days (Fig. S1†).

The crystal structure of  $\text{KMnCuTe}_2$  is also related to that of the  $\text{BaM}_x\text{Te}_2$  system ( $\text{M} = \text{Cu}$  and  $\text{Ag}$ ) reported by Jana *et al.*<sup>37</sup> Both  $\text{KMnCuTe}_2$  and  $\text{BaM}_x\text{Te}_2$  are composed of the edge-sharing tetrahedral layers, in which the Mn(Cu)–Te bond length is slightly smaller than the Cu–Te bonds in  $\text{BaCu}_{0.43}\text{Te}_2$  ( $2.72\text{--}2.74 \text{ \AA}$ ).<sup>37</sup> Different from the alternating stacking of  $\text{K}^+$  and  $[\text{Mn}(\text{Cu})\text{Te}_4]$  layers in  $\text{KMnCuTe}_2$ , the  $[\text{Cu}_x\text{Te}_4]$  tetrahedral layers are separated by both  $\text{Ba}^{2+}$  cations and Te square planes in  $\text{BaCu}_x\text{Te}_2$ . A modulated structure was also observed in  $\text{BaM}_x\text{Te}_2$  due to the distorted Te square nets, but no modulated structure has been found in  $\text{AMnMCh}_2$  system yet.

As we mentioned,  $\text{KMnCuTe}_2$  is a new member in  $\text{AMnMCh}_2$  family, and ascribing to the large radius of Te, both  $a$  and  $c$  lattice constants of  $\text{KMnCuTe}_2$  are much larger than those of the sulfides and selenides in  $\text{AMnMCh}_2$ , as shown in Table 1. Only the reported  $\text{CsMn}_{1.18}\text{Ag}_{0.64}\text{Te}_2$  shows larger lattice parameters than  $\text{KMnCuTe}_2$ , but the related physical property was not described.<sup>23</sup> The metal–metal distance in  $ab$  plane, which equals to  $\frac{\sqrt{2}}{2}a$ , is also listed in Table 1. The Mn(Cu)–Mn(Cu) distance is  $3.049 \text{ \AA}$  in  $\text{KMnCuTe}_2$  (Fig. 2), which is much

Table 1 Structure parameters and magnetic behavior of  $\text{KMnCuTe}_2$  compared to the other  $\text{AMnMCh}_2$  in previous works (SG = spin-glass state, PM = paramagnetism and AFM = antiferromagnetism)

Composition	$a$ (Å)	$c$ (Å)	Metal–metal distances (Å)	MT	Ref.
$\text{KMnCuS}_2$	3.9596(6)	13.297(3)	2.800	SG	16
$\text{RbMnCuS}_2$	4.0001(3)	13.624(2)	2.828	SG	16
$\text{CsMnCuS}_2$	4.0514(3)	14.147(2)	2.865	SG	16
$\text{KMnCuSe}_2$	4.0912(8)	13.893(4)	2.893	SG	17
$\text{RbMnCuSe}_2$	4.1283(6)	14.169(3)	2.919	PM	17
$\text{CsMnCuSe}_2$	4.1902(5)	14.686(3)	2.963	PM	17
$\text{KMnAgSe}_2$	4.2486(3)	13.943(2)	3.004	SG	18
<b><math>\text{KMnCuTe}_2</math></b>	<b>4.3115(3)</b>	<b>14.9360(20)</b>	<b>3.049</b>	<b>AFM</b>	<b>This work</b>
$\text{CsMn}_{1.18}\text{Ag}_{0.64}\text{Te}_2$	4.520(2)	15.484(8)	3.196	Not mentioned	23

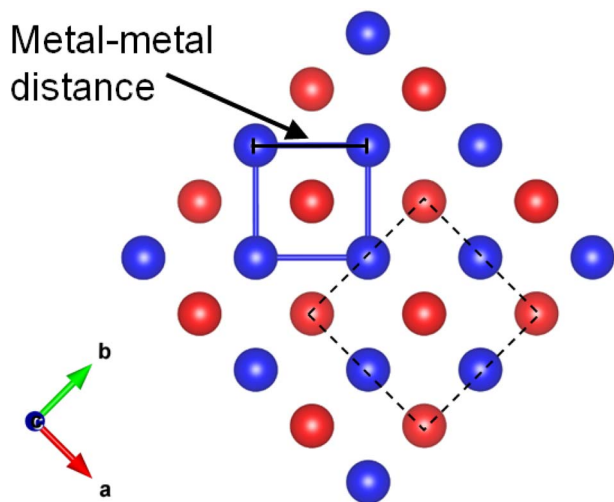


Fig. 2 The metal–metal distance along the layer direction in  $\text{ThCr}_2\text{Si}_2$ -type compounds. The dash square is the unit cell of the structure.

longer than those in  $\text{KMnCuSe}_2$  (2.893 Å) and  $\text{KMnCuS}_2$  (2.800 Å),<sup>16,17</sup> and is also longer than the  $\text{Mn}(\text{Ag})$ – $\text{Mn}(\text{Ag})$  bond in  $\text{KMnAgSe}_2$  (3.004 Å).<sup>18</sup> This demonstrates a very weak interaction between the metal atoms in tetrahedral layers in  $\text{KMnCuTe}_2$ . It has been widely believed that the structure parameter, especially the metal–metal distance, plays an important role on the magnetic and transport properties of  $\text{AMnMCh}_2$  compounds. With the relatively large metallic distance in layer,  $\text{KMnCuTe}_2$  provides an important platform to understand the structure–property relationship of  $\text{AMnMCh}_2$  materials, which will be discussed in details below.

To investigate the influence of the large lattice parameters on magnetic properties, we performed the measurements on temperature dependent magnetic susceptibility ( $M$ – $T$  curve) of  $\text{KMnCuTe}_2$ . As shown in Fig. 3, the magnetic susceptibility shows a broad transition at around 225 K, suggesting a low-dimensional AFM interaction. Meanwhile, a kink was also observed at about 122 K in the  $M$ – $T$  curve. In high temperature range, the magnetic susceptibility deviates from the Curie–Weiss law, implying the complex magnetic interactions between  $\text{Mn}^{2+}$  ions at high temperatures. The absence of the bifurcate between the zero-field cooling (ZFC) and field cooling (FC) curves in low temperature range rules out the spin-glass behavior, different from magnetic states of  $\text{KMnCuSe}_2$  and  $\text{KMnCuS}_2$ . It is worth noting that although this low-dimensional AFM ordering is unique in  $\text{AMnMCh}_2$  family, the similar magnetic behavior was observed in some layered transition metal oxychalcogenides such as  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ .<sup>38</sup> The Curie–Weiss-like upturn in low temperature range is presumably due to the paramagnetic impurities on the surface of  $\text{KMnCuTe}_2$  crystal. The magnetization loop at 10 K is also shown in inset of Fig. 3a, which exhibit linear dependence on the field ( $H$ ) with basically no hysteresis, further confirming the AFM ordering in this compound.

In our previous work, it was observed that the magnetism in Fe-based  $\text{AFMCh}_2$  family is mainly determined by the  $a$  lattice

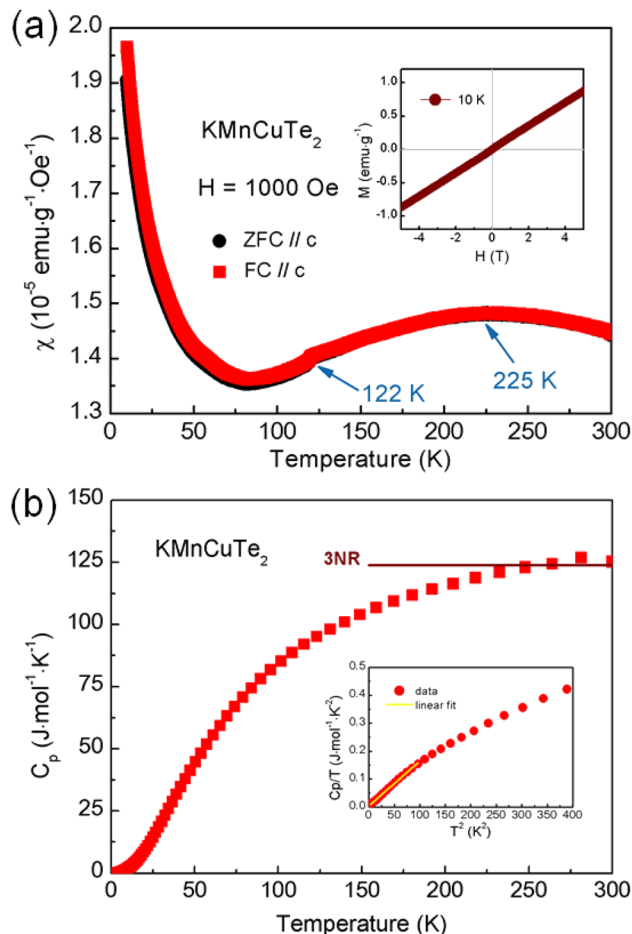


Fig. 3 (a) Temperature dependence of magnetic susceptibility for  $\text{KMnCuTe}_2$  single crystals from 300 to 10 K with the applied field ( $H = 1000$  Oe) parallel to the  $c$  axis. Inset shows field dependence of magnetic susceptibility at 10 K. (b) Temperature dependence of specific heat capacity  $C_p$  of  $\text{KMnCuTe}_2$  from 300 to 2 K. The inset shows the relation between  $C_p/T$  and  $T^2$  in low temperature range (<20 K) with the linear fitting plotted as yellow line.

constant, where the long-range AFM order can only be maintained with the  $a$  axis larger than 4.19 Å while the spin-glass behavior turns to appear with the  $a$  axis smaller than this critical value.<sup>22</sup> Interestingly, the AFM interaction observed in  $\text{KMnCuTe}_2$  demonstrates the similar regulation rule of the  $a$  lattice parameter over the magnetic behavior of  $\text{AMnMCh}_2$  compounds with the critical value as  $\sim 4.3$  Å (Table 1), implying the uniform mechanism of the structural modulation on magnetic coupling in  $\text{ThCr}_2\text{Si}_2$ -type material family with different transition metals.

The heat capacity *versus*  $T$  ( $C_p$ – $T$  curve) was plotted in Fig. 3b. However, there is no clear anomaly observed in  $C_p$ – $T$  curve at the AFM transition temperature (225 K). This phenomenon could be corresponding to the broad transition in  $M$ – $T$  curve and suggests that the magnetic entropies above transition temperature decreases gradually during the cooling process. As shown in the inset of Fig. 3b, the  $C_p(T)/T$  *versus*  $T^2$  shows a non-linear characteristic at low temperature (below 20 K). By fitting the data below 10 K with the expression:  $C_p/T = \gamma + \beta T^2$ , where  $\gamma$





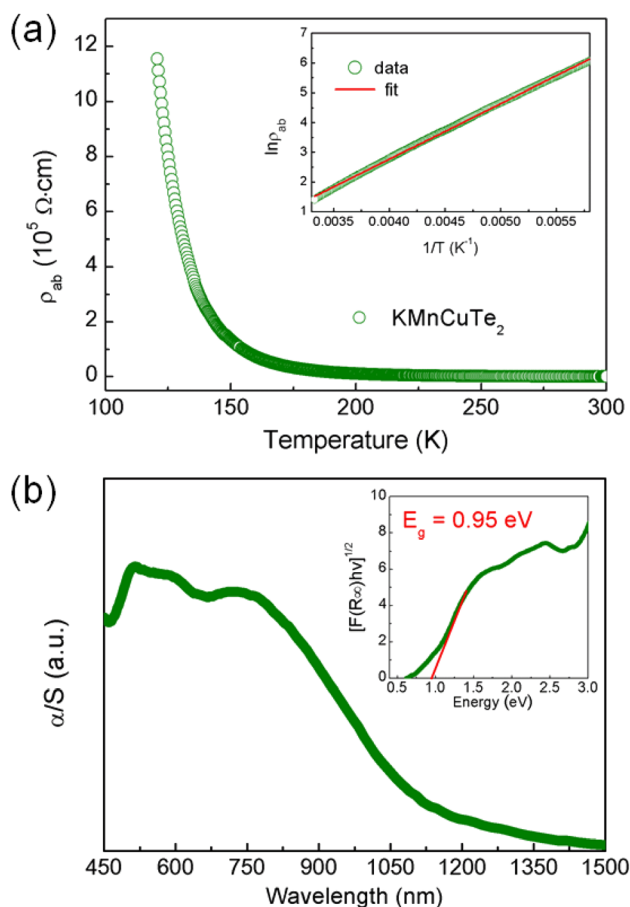


Fig. 4 (a) Temperature dependence of the in-plane resistivity for KMnCuTe<sub>2</sub> single crystal from 300 to 120 K. Inset shows the fitted result for the data in high temperature range from 300 to 150 K using the thermal activation model. (b) UV-vis diffuse reflectance spectrum of KMnCuTe<sub>2</sub>. Inset shows the extracted indirect band gap according to Tauc plot.

is the Sommerfeld coefficient, the fitted  $\gamma$  and  $\beta$  were obtained as  $3.35 \text{ mJ mol}^{-1} \text{ K}^{-2}$  and  $1.60 \text{ mJ mol}^{-1} \text{ K}^{-4}$ , respectively. According to the formula  $\theta_D = (12\pi^4 NR/\beta)^{1/3}$ , the Debye temperature  $\theta_D$  is estimated to be about 182 K.

The variation of in-plane resistivity with temperature for KMnCuTe<sub>2</sub> crystal is shown in Fig. 4a. Clearly it exhibits a semiconducting behavior from 120 K to 300 K. The resistivity data obey the thermally activated behavior  $\rho = \rho_0 \exp(E_a/k_B T)$  as shown in inset, and the activation energy  $E_a$  is calculated as 0.16 eV. The electrical resistivity at room temperature is around  $408 \text{ } \Omega \text{ cm}$ , which is much larger than those of KMnCuSe<sub>2</sub> and KMnCuS<sub>2</sub>. It is generally believed that the telluride shows smaller resistivity than its analogous selenide and sulfide due to the smaller electronegativity of Te. We indicate that the abnormal rules in KMnCuTe<sub>2</sub> compared to KMnCuSe<sub>2</sub> and KMnCuS<sub>2</sub> could be resulted from the long metal-metal distance, which weakens the metallic orbital overlap between Mn(Cu) atoms and significantly increases the in-plane resistivity. It is noticed that in-plane resistivity of KMnCuTe<sub>2</sub> is also larger than those of KFeCuTe<sub>2</sub> and KFeAgTe<sub>2</sub>, suggesting the significant effect of transition metal species on electrical properties of ThCr<sub>2</sub>Si<sub>2</sub>-type compounds.<sup>12,13,20</sup>

The UV-vis diffuse reflectance spectrum was collected to show the optical property of KMnCuTe<sub>2</sub> crystals. To extract the band gap, the reflectance data were transformed to pseudo-absorption data using Kubelka-Munk equation as described in the experimental section (Fig. 4b). The optical band gap was extracted using the indirect model as suggested by the band structure calculation described below, and the obtained band gap ( $E_g$ ) is 0.95 eV, which is consistent with the black color of the crystal. Hence it can be concluded that KMnCuTe<sub>2</sub> is an antiferromagnetic semiconductor with the narrow band gap.

The density functional theory calculations were also carried out to better understand the nature of magnetism and

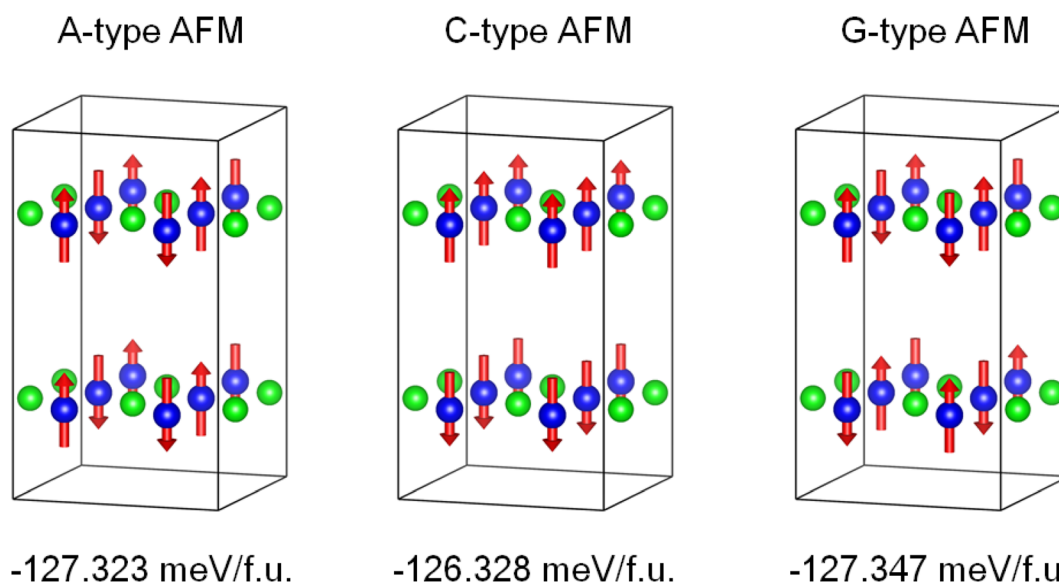


Fig. 5 The calculated energies of different AFM structures of KMnCuTe<sub>2</sub> in a  $2 \times 2 \times 1$  supercell, showing that the G-type AFM is the energy favorable ground state of KMnCuTe<sub>2</sub>.

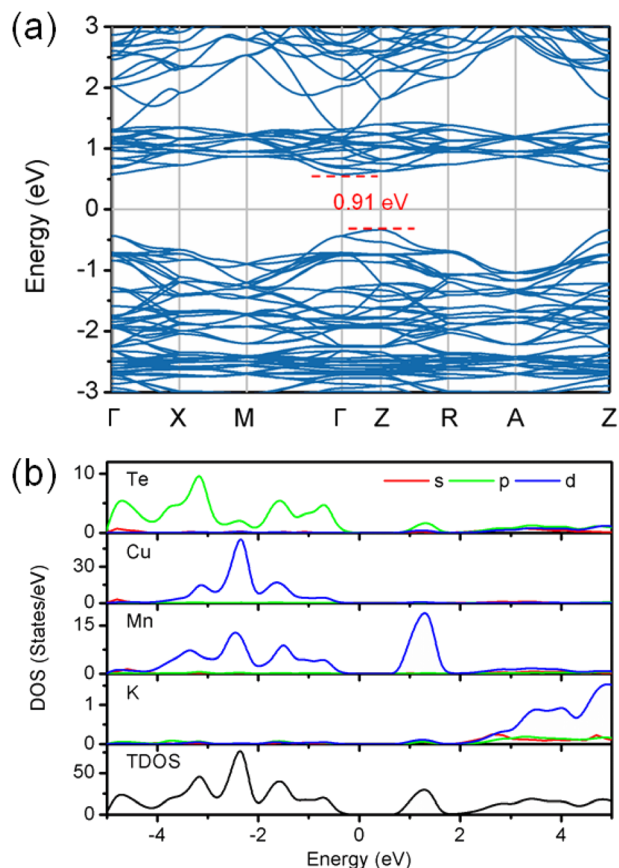


Fig. 6 (a) The calculated electronic band structure and (b) density of states for KMnCuTe<sub>2</sub>.

electronic structure of KMnCuTe<sub>2</sub>. Three AFM structures, including A-type, C-type and G-type were built in a  $2 \times 2 \times 1$  supercell as shown in Fig. 5, and the calculation suggested the G-type AFM as the energy favorable ground state of KMnCuTe<sub>2</sub>. It should be mentioned that the energy difference to the A-type AFM state is only 0.024 meV per f.u., suggesting that the A-type AFM can also be the possible ground state of KMnCuTe<sub>2</sub>. With the G-type AFM structure, the electronic band structure and density of states of KMnCuTe<sub>2</sub> were calculated. As shown in Fig. 6a, the valence band maximum (VBM) is located at Z point while the conduction band minimum (CBM) is located at  $\Gamma$ , indicating that KMnCuTe<sub>2</sub> is an indirect semiconductor. The calculated band gap is 0.91 eV, in consistent with the experimental result (0.95 eV). Based on the partial electronic density of states (DOS) shown in Fig. 6b, the valence band of KMnCuTe<sub>2</sub> near the Fermi level ( $E_F$ ) is contributed by the orbitals of Mn, Cu and Te, while the conduction band near the band edge is mainly composed of the 3d orbitals of Mn.

## Conclusion

Here we report a new quaternary chalcogenide KMnCuTe<sub>2</sub> which exhibits layered structure and antiferromagnetic semiconducting behavior. As a new member in AMnMCh<sub>2</sub> (A = K, Rb, Cs, M = Cu, Ag and Ch = S, Se, Te) material family,

KMnCuTe<sub>2</sub> adopts the ThCr<sub>2</sub>Si<sub>2</sub>-type structure with mixed Mn and Cu occupation. The refined lattice parameters ( $a = 4.3115(3)$  Å and  $c = 14.9360(20)$  Å) and resulted metal–metal distance (3.049 Å) are larger than the sulfides and selenides in AMnMCh<sub>2</sub>. KMnCuTe<sub>2</sub> shows a long-range G-type antiferromagnetic interaction with the transition temperature at around 225 K, very unique in the AMnMCh<sub>2</sub> system. The resistivity and diffuse reflectance spectra indicate that KMnCuTe<sub>2</sub> is an indirect semiconductor with the optical band gap as 0.95 eV. These results shed light on the relationship between crystal structure and physical properties of ThCr<sub>2</sub>Si<sub>2</sub>-type materials.

## Conflicts of interest

The authors declare no competing financial interest.

## Acknowledgements

The financial supports by the National Natural Science Foundation of China (No. 51872028 and 51832010) are gratefully acknowledged.

## References

- 1 J. G. Guo, S. F. Jin, G. Wang, S. C. Wang, K. X. Zhu, T. T. Zhou, M. He and X. L. Chen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2010, **82**, 180520.
- 2 T. P. Ying, X. L. Chen, G. Wang, S. F. Jin, T. T. Zhou, X. F. Lai, H. Zhang and W. Y. Wang, *Sci. Rep.*, 2012, **2**, 1–7.
- 3 T. P. Ying, X. L. Chen, G. Wang, S. F. Jin, X. F. Lai, T. T. Zhou, H. Zhang, S. J. Shen and W. Y. Wang, *J. Am. Chem. Soc.*, 2013, **135**, 2951–2954.
- 4 Z. N. Guo, F. Sun and W. X. Yuan, *Cryst. Growth Des.*, 2017, **17**, 2238–2253.
- 5 J. R. Neilson, A. Llobet, A. V. Stier, L. Wu, J. J. Wen, J. Tao, Y. M. Zhu, Z. B. Tesanovic, N. P. Armitage and T. M. McQueen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2012, **86**, 054512.
- 6 J. R. Neilson and T. M. McQueen, *J. Am. Chem. Soc.*, 2012, **134**, 7750–7757.
- 7 G. Huan, M. Greenblatt and M. Croft, *Eur. J. Inorg. Chem.*, 1989, **26**, 193–220.
- 8 J. H. Yang, B. Chen, H. D. Wang, Q. H. Mao, M. Imai, K. Yoshimura and M. H. Fang, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2013, **88**, 064406.
- 9 Z. N. Guo, H. H. Zhang, D. Wang, B. L. Han, S. F. Jin and W. X. Yuan, *Dalton Trans.*, 2016, **45**, 8248–8252.
- 10 C. Mujica, J. Páez and J. Llanos, *Mater. Res. Bull.*, 1994, **29**, 263–268.
- 11 M. Oledzka, K. V. Ramanujachary and M. Greenblatt, *Mater. Res. Bull.*, 1996, **31**, 1491–1499.
- 12 H. C. Lei, E. S. Bozin, K. Wang and C. Petrovic, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **84**, 060506.
- 13 H. Ryu, H. C. Lei, B. Klobes, J. B. Warren, R. P. Hermann and C. Petrovic, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2015, **91**, 174517.



- 14 D. D. Yuan, N. Liu, K. K. Li, S. F. Jin, J. G. Guo and X. L. Chen, *Inorg. Chem.*, 2017, **56**, 13187–13193.
- 15 M. Oledzka, J. G. Lee, K. V. Ramanujachary and M. Greenblatt, *J. Solid State Chem.*, 1996, **127**, 151–160.
- 16 M. Oledzka, J. G. Lee, K. V. Ramanujachary and M. Greenblatt, *Mater. Res. Bull.*, 1997, **32**, 889–898.
- 17 M. Oledzka, K. V. Ramanujachary and M. Greenblatt, *Mater. Res. Bull.*, 1998, **33**, 855–866.
- 18 X. F. Lai, S. F. Jin, X. Chen, T. T. Zhou, T. P. Ying, H. Zhang and S. J. Shen, *Mater. Express*, 2014, **4**, 343–348.
- 19 H. R. Heulings IV, J. Li and D. M. Proserpio, *Main Group Met. Chem.*, 1998, **21**, 225–230.
- 20 F. Sun, Z. N. Guo, N. Liu, K. Lin, D. Wang and W. X. Yuan, *Dalton Trans.*, 2017, **46**, 3649–3654.
- 21 X. N. Sun, Y. P. Song, J. Deng, S. F. Jin and X. L. Chen, *Dalton Trans.*, 2019, **48**, 17572–17578.
- 22 B. B. Wang, Z. N. Guo, F. Sun, J. Deng, J. W. Lin, D. Wu and W. X. Yuan, *J. Solid State Chem.*, 2019, **272**, 126–130.
- 23 E. J. Wu, M. A. Pell and J. A. Ibers, *Acta Crystallogr.*, 1996, **C52**, 2384–2385.
- 24 J. Li, H. Y. Guo and R. A. Yglesias, *Chem. Mater.*, 1995, **7**, 599–601.
- 25 Z. N. Guo, Z. Liu, J. Deng, J. W. Lin, Z. J. Zhang, X. Han, F. Sun and W. X. Yuan, *J. Alloys Compd.*, 2021, **883**, 160820.
- 26 R. Ang, K. Nakayama, W. G. Yin, T. Sato, H. C. Lei, C. Petrovic and T. Takahashi, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2013, **88**, 155102.
- 27 Y. Song, H. B. Cao, B. C. Chakoumakos, Y. Zhao, A. F. Wang, H. C. Lei, C. Petrovic and R. J. Birgeneau, *Phys. Rev. Lett.*, 2019, **122**, 087201.
- 28 Y. Song, D. S. Yuan, X. Y. Lu, Z. J. Xu, E. Bourret-Courchesne and R. J. Birgeneau, *Phys. Rev. Lett.*, 2019, **123**, 247205.
- 29 V. Petříček, M. Dušek and L. Palatinus, *Z. Kristallogr. – Cryst. Mater.*, 2014, **229**, 345–352.
- 30 L. F. Gate, *Appl. Opt.*, 1974, **13**, 236–238.
- 31 G. Kresse and J. Furthmüller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 32 G. Kresse and J. Furthmüller, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169.
- 33 J. P. Predew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 34 G. Kresse and D. Joubert, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 1758–1775.
- 35 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1975, **13**, 5188–5192.
- 36 A. Jain, G. Hautier, S. P. Ong, C. J. Moore, C. C. Fischer, K. A. Persson and G. Ceder, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **84**, 045115.
- 37 S. Jana, M. Ishtiyak, G. Panigrahi, J. Prahsh, A. Mesbah, S. Gueddida, S. Lebegue, C. D. Malliakas and J. A. Ibers, *Inorg. Chem.*, 2020, **59**, 12276–12285.
- 38 T. T. Zhou, Y. M. Wang, S. F. Jin, D. D. Li, X. F. Lai, T. P. Ying, H. Zhang, S. J. Shen, W. J. Wang and X. L. Chen, *Inorg. Chem.*, 2014, **53**, 4154–4160.

