



Cite this: *Chem. Commun.*, 2023, 59, 1677

Received 6th December 2022,  
Accepted 17th January 2023

DOI: 10.1039/d2cc06655f

[rsc.li/chemcomm](http://rsc.li/chemcomm)

**Dissolved transition metal ions can induce peak shifts in the NMR spectra of degraded battery electrolytes. Here, we exploit this straightforward, accessible method to calculate magnetic moments for dissolved  $\text{Ni}^{2+}$ ,  $\text{Mn}^{2+}$ ,  $\text{Co}^{2+}$ , and  $\text{Cu}^{2+}$ ; subsequent analysis of dissolution from  $\text{LiMn}_2\text{O}_4$ ,  $\text{LiNiO}_2$ , and  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  shows that the dissolved metals are exclusively divalent.**

Transition metal dissolution and deposition is a significant contributor to capacity fade in lithium-ion cells.<sup>1–4</sup> There are limited direct measurements of the oxidation states of dissolved transition metals, but such measurements are typically performed *via* XANES of the electrolyte solution and/or separator.<sup>5–10</sup> This yields only an average oxidation state,<sup>7,8</sup> and XANES measurements often require synchrotron access. EPR spectroscopy has been used to distinguish  $\text{Mn}^{2+}$  from  $\text{Mn}^{3+}$ ,<sup>7,11,12</sup> although this assumes all  $\text{Mn}^{2+}$  is EPR-observable and all inconsistency between EPR and ICP-OES results is due to the presence of EPR-silent  $\text{Mn}^{3+}$ —an approach which has been questioned due to the potential EPR silence of some  $\text{Mn}^{2+}$  complexes.<sup>13</sup> More generally, EPR of metals with either rapid electronic relaxation or with integer spins,  $S$ , including  $\text{Co}^{2+}$  ( $S = 3/2$ ) and  $\text{Ni}^{2+}$  complexes ( $S = 1$ ),<sup>14</sup> can be challenging.<sup>15</sup> Capillary electrophoresis is a promising method that has been used to determine oxidation states of dissolved  $\text{Mn}$ ,<sup>16</sup>  $\text{Fe}$ ,<sup>17</sup> and  $\text{Cu}$ .<sup>18</sup> Electrochemical methods may also be used to infer metal oxidation states.<sup>19–21</sup>

It is thought that most 3d metals dissolve from cathodes as  $\text{M}^{2+}$ ,<sup>10,22–25</sup> however, this is of increasing debate. While EPR, XANES, and electrochemical studies<sup>7,8,11,12,21</sup> of  $\text{LiMn}_2\text{O}_4$  and/or  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  have observed some fraction of dissolved  $\text{Mn}^{3+}$ , other XANES, XPS, and capillary electrophoresis/

## Determining the oxidation states of dissolved transition metals in battery electrolytes from solution NMR spectra†

Jennifer P. Allen <sup>ab</sup> and Clare P. Grey <sup>ab</sup>

UV-visible studies have shown only  $\text{Mn}^{2+}$ ,<sup>5,9,16</sup> XANES of  $\text{LiNi}_{0.5}\text{Mn}_{0.3}\text{Co}_{0.2}\text{O}_2$  found dissolved  $\text{Ni}^{2+}$  and  $\text{Mn}^{2+}$  but  $\text{Co}^{3+}$ ,<sup>6</sup> XANES of  $\text{LiNi}_{0.33}\text{Mn}_{0.33}\text{Co}_{0.33}\text{O}_2$  found dissolved  $\text{Mn}^{2+}$  (and deposited  $\text{Mn}^{2+}$ ,  $\text{Ni}^{2+}$ , and  $\text{Co}^{2+}$ ).<sup>10</sup> Dissolved  $\text{Cu}^+$  and  $\text{Cu}^{2+}$  (from current collectors) and  $\text{Fe}^{2+}$  and  $\text{Fe}^{3+}$  (from  $\text{LiFePO}_4$ ) have all been observed.<sup>17,18</sup>

Most of the dissolved metal ions are paramagnetic and in the NMR spectra of electrolytes containing these metals, the paramagnetic species cause bulk magnetic fields and changes in all NMR chemical shifts away from their positions in diamagnetic solutions, known as bulk magnetic susceptibility (BMS) shifts. These BMS shifts are not observed with an internal reference, as the reference is also affected, but it may be observed if the reference is not in contact with the paramagnetic solution, *e.g.*, by using a sufficiently thick-walled solvent capillary.<sup>14,26,27</sup> For a cylindrical sample in a superconducting magnet, neglecting the diamagnetic contribution, the molar magnetic susceptibility of a paramagnetic solute ( $\chi_M$ ,  $\text{mL}\cdot\text{mol}^{-1}$ ) depends on the BMS shift it induces ( $\Delta\nu$ , Hz), the spectrometer frequency ( $\nu_0$ , Hz), and the metal concentration ( $c$ ,  $\text{mol}\cdot\text{mL}^{-1}$ ) *via* eqn (1).

$$\chi_M = \frac{3\Delta\nu}{4\pi\nu_0 c} \quad (1)$$

If the temperature  $T$  is known, then the effective magnetic moment  $\mu_{\text{eff}}$  can be calculated (eqn (2)) and compared to the theoretical spin-only magnetic moment  $\mu_s$ , which is dependent on the number of unpaired electrons  $n$  (eqn (3)).<sup>14,28</sup> Hence,  $\mu_{\text{eff}}$  may permit identification of the oxidation state and spin state of paramagnetic compounds.

$$\mu_{\text{eff}} = \sqrt{\frac{3k_B}{N_A\mu_B^2}\chi_M T} = 2.83\sqrt{\chi_M T} \quad (2)$$

$$\mu_s = \sqrt{n(n+2)} \quad (3)$$

Notably,  $\mu_s$  does not account for spin-orbit coupling or orbital contributions to the magnetic moment, and  $\mu_{\text{eff}}$  deviates

<sup>a</sup> Yusuf Hamied Department of Chemistry, University of Cambridge, Cambridge, Lensfield Road, CB2 1EW, Cambridge, UK. E-mail: cpg27@cam.ac.uk

<sup>b</sup> The Faraday Institution, Quad One, Harwell Science and Innovation Campus, Didcot OX11 0RA, UK

† Electronic supplementary information (ESI) available: Methods, Fig. 1 fits,  $\mu_{\text{eff}}$  values,  $\text{LiMn}_2\text{O}_4$  storage,  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  ICP-OES. See DOI: <https://doi.org/10.1039/d2cc06655f>



from  $\mu_s$  when such contributions occur.<sup>28,29</sup> The magnetic moment accounting for orbital contribution is shown in eqn (4), which simplifies to  $\mu_s$  when  $L = 0$  (eqn (3), as  $S = n/2$ ). The  $\mu_{\text{eff}}$  of a sample can also be interpreted via comparison to  $\mu_{\text{eff}}$  of known compounds.<sup>29,30</sup>

$$\mu_{S+L} = \sqrt{4S(S+1) + L(L+1)} \quad (4)$$

This work uses  $^1\text{H}$  BMS shifts of solvent peaks to characterise dissolved transition metals in a typical electrolyte solution, 1 M LiPF<sub>6</sub> in 3:7 ethylene carbonate : ethyl methyl carbonate (EC:EMC, v/v). Trifluoromethanesulfonimide (TFSI) salts were used to model dissolved Mn<sup>2+</sup>, Co<sup>2+</sup>, Ni<sup>2+</sup>, and Cu<sup>2+</sup>. NMR spectra of diamagnetic and paramagnetic electrolyte solutions were measured separately (referenced to C<sub>6</sub>D<sub>6</sub> capillaries) and the BMS shift was extracted by comparison. Metal dissolution from LiMn<sub>2</sub>O<sub>4</sub>, LiNiO<sub>2</sub>, and LiNi<sub>0.5</sub>Mn<sub>1.5</sub>O<sub>4</sub> was characterised by storing cathode powders with electrolyte, after which isolated solutions were analysed with NMR and ICP-OES. Additional experimental details are provided in the ESI,† including a diagram of the NMR tube with solvent capillary (Fig. S1, ESI†).

To evaluate the method's sensitivity, magnetic susceptibility calibration curves were constructed from electrolyte samples containing different concentrations (0.01, 0.05, 0.1, 0.5, 1, 3, and 5 mM) of Mn(TFSI)<sub>2</sub> or Ni(TFSI)<sub>2</sub> (Fig. 1).

Only the 0.5, 1, 3, and 5 mM measurements are shown in Fig. 1, as the  $^1\text{H}$  BMS shift upon addition of 0.1 mM of Mn(TFSI)<sub>2</sub> or Ni(TFSI)<sub>2</sub> is below the limit of detection (LoD) of our experiments; peak shifts at smaller concentrations are negligible. Total magnetic susceptibility  $\chi$  is presented rather than molar magnetic susceptibility  $\chi_M$  (*i.e.*, eqn (1) is applied but without dividing by  $c$ ). Values increase linearly with metal concentration, with good fits from all four peaks (data for fits in (f)–(i) are shown in ESI,† Table S1), indicating that the measurement is reliable for metal concentrations  $\geq 0.5$  mM.

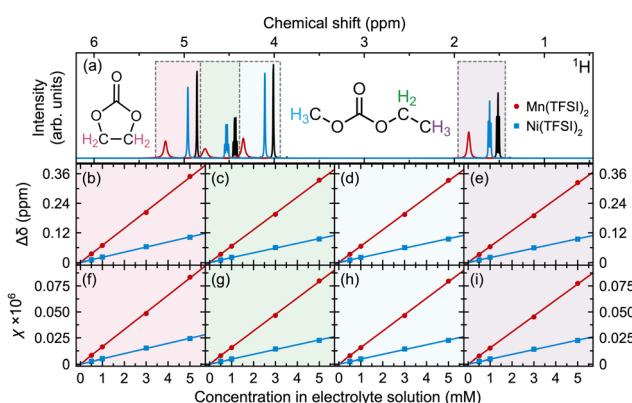


Fig. 1 (a)  $^1\text{H}$  NMR spectra, (b)–(e) peak shifts, and (f)–(i) magnetic susceptibilities ( $\chi$ , calculated as in eqn (1) but without dividing by concentration,  $c$ ), for electrolyte solutions containing Mn(TFSI)<sub>2</sub> or Ni(TFSI)<sub>2</sub>. Spectra are shown for the electrolyte without (black) and with 5 mM Mn<sup>2+</sup> (red) or Ni<sup>2+</sup> (blue). Panels correspond to (b) and (f) EC CH<sub>2</sub>, (c) and (g) EMC ethyl CH<sub>2</sub>, (d) and (h) EMC methyl, and (e) and (i) EMC ethyl CH<sub>3</sub> resonances, shaded with the same colours as used for the protons in the EC and EMC molecules shown in (a).

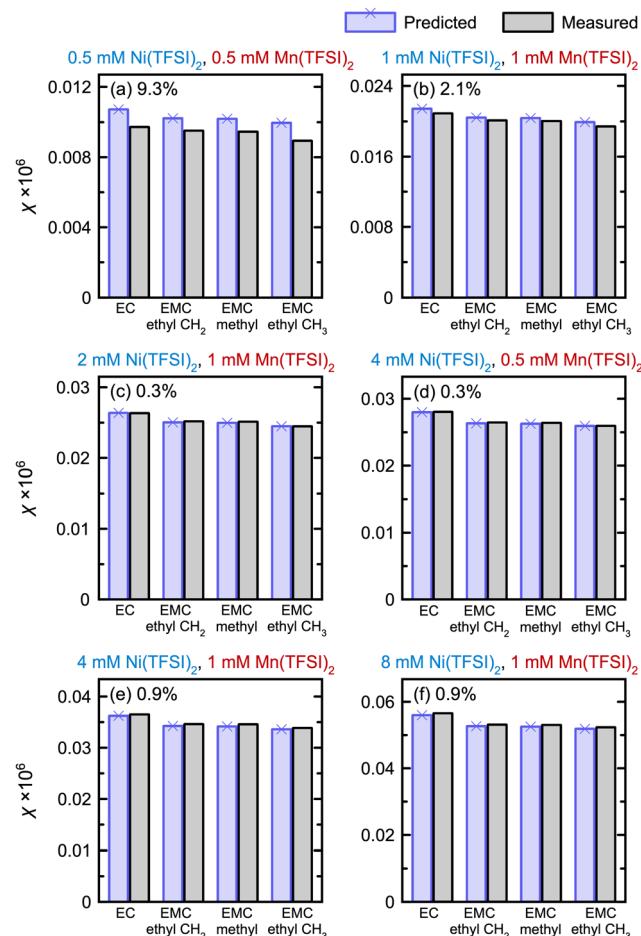


Fig. 2 (a)–(f) Magnetic susceptibilities of solutions containing different amounts of Mn(TFSI)<sub>2</sub> and Ni(TFSI)<sub>2</sub> added to electrolyte solutions. Percentages give the average error of the four predicted values from the four  $^1\text{H}$  resonances, as compared to the four measured values for each sample.

The LoD was estimated by calculating  $\mu_{\text{eff}}$  for each sample. At concentrations  $\geq 0.5$  mM,  $\mu_{\text{eff}} = 3.3\text{--}3.4 \mu_{\text{B}}$  for Ni<sup>2+</sup> and 6.0–6.1  $\mu_{\text{B}}$  for Mn<sup>2+</sup>, but this differed by 14–18% at 0.1 mM (3.8  $\mu_{\text{B}}$  for Ni<sup>2+</sup> and 4.9  $\mu_{\text{B}}$  for Mn<sup>2+</sup>); hence, the LoD is in the 0.1–0.5 mM range. We note that small differences in peak positions may arise from small variations in the magnetic field (*e.g.*, from different shimming or placement of samples in NMR tubes) as the diamagnetic and paramagnetic spectra were measured in separate samples and referenced to each other *via* C<sub>6</sub>D<sub>6</sub> capillaries. This variation may be reduced by incorporating the diamagnetic and paramagnetic electrolytes into one sample, by using a reference capillary of deuterated diamagnetic electrolyte, which may increase the sensitivity of the method.

To evaluate the method's ability to measure samples containing more than one dissolved metal, solutions were prepared containing both Mn(TFSI)<sub>2</sub> and Ni(TFSI)<sub>2</sub>. Fig. 2 shows the total predicted and observed magnetic susceptibilities of these samples, where predicted magnetic susceptibilities are calculated using the correlations determined in Fig. 1(f)–(i).

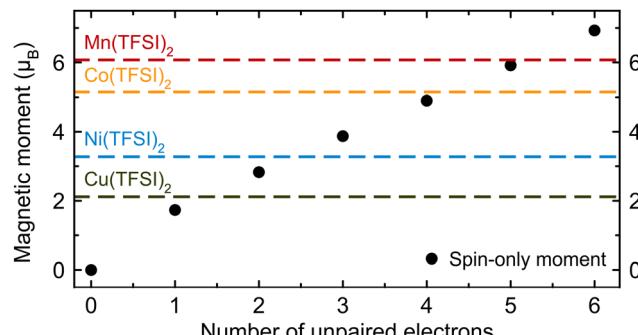


Fig. 3 Effective magnetic moments (dashed lines) for dissolved  $\text{Mn}(\text{TFSI})_2$ ,  $\text{Co}(\text{TFSI})_2$ ,  $\text{Ni}(\text{TFSI})_2$ , and  $\text{Cu}(\text{TFSI})_2$ , calculated from the BMS shift of the  ${}^1\text{H}$  EMC ethyl  $\text{CH}_3$  peak. Black points show the theoretical values of the spin-only magnetic moment for different numbers of unpaired electrons. Electrolyte solutions contained 5 mM  $\text{M}(\text{TFSI})_2$ .

The susceptibilities for samples containing both  $\text{Ni}^{2+}$  and  $\text{Mn}^{2+}$  in Fig. 2 are consistent with the calibrations generated from single metals, showing the BMS method is additive. While the error is 9.3% in a solution containing 1 mM paramagnetic ions total, this drops to 2.1% in a solution containing 2 mM paramagnetic ions; all other samples, with 3–9 mM metal ions, have <1% error. Hence, it is important to have a sufficient concentration of metal ions for accurate measurement.

Magnetic susceptibilities were then used to determine magnetic moments (eqn (1) and (2)) for a series of paramagnetic ions often found in battery electrolytes. Fig. 3 shows  $\mu_{\text{eff}}$  for dissolved  $\text{Mn}(\text{TFSI})_2$ ,  $\text{Ni}(\text{TFSI})_2$ ,  $\text{Co}(\text{TFSI})_2$ , and  $\text{Cu}(\text{TFSI})_2$  (values listed in ESI,† Table S2), calculated from the EMC ethyl  $\text{CH}_3$  shift of 5 mM solutions;  $\mu_s$  is also shown for comparison.

For  $\text{d}^5 \text{Mn}(\text{TFSI})_2$ ,  $\mu_{\text{eff}} = 6.07 \mu_{\text{B}}$ , which is close to the  $n = 5$  ( $S = 5/2$ ) value of  $\mu_s$ ,  $5.92 \mu_{\text{B}}$ . For  $\text{Cu}(\text{TFSI})_2$ ,  $\text{Ni}(\text{TFSI})_2$ , and  $\text{Co}(\text{TFSI})_2$ ,  $\mu_{\text{eff}} > \mu_s$  by 0.38, 0.45, and  $1.27 \mu_{\text{B}}$ , respectively. These larger values arise because  $\mu_s$  does not account for spin-orbit coupling or orbital contributions,<sup>28,29</sup> but for  $\text{Mn}^{2+}$ ,  $L = 0$  and  $\mu_{s+L} = \mu_s$  (eqn (3)–(4)). If  $\text{Co}^{2+}$  ( $d^7$ ,  $S = 3/2$ ,  $L = 3$ ),  $\text{Ni}^{2+}$  ( $d^8$ ,  $S = 1$ ,  $L = 3$ ), and  $\text{Cu}^{2+}$  ( $d^9$ ,  $S = 1/2$ ,  $L = 2$ ) were free ions with degenerate d orbitals, all would show orbital contributions to  $\mu_{\text{eff}}$ . If a tetrahedral field splitting occurred, only  $\text{Ni}^{2+}$  and  $\text{Cu}^{2+}$  would have an orbital contribution. Instead, the large deviation from  $\mu_s$  for  $\text{Co}^{2+}$  only is consistent with an octahedral splitting, where orbital contribution to the magnetic moment is quenched to first order for  $\text{Ni}^{2+}$  ( $t_{2g}^6 e_g^2$ ) and  $\text{Cu}^{2+}$  ( $t_{2g}^6 e_g^3$ ), but not  $\text{Co}^{2+}$  ( $t_{2g}^5 e_g^2$ ).<sup>28</sup> The smaller deviation from  $\mu_s$  for  $\text{Ni}^{2+}$  and  $\text{Cu}^{2+}$  is then due to mixing in of excited states *via* spin-orbit coupling. Although tetrahedral and octahedral splitting are simplifications due to the complex solvation environment, the splitting suggests paramagnetic ions are approximately six-coordinate. The  $\mu_{\text{eff}}$  values in Fig. 3 are also consistent with literature values for these ions.<sup>30</sup> The BMS shift is therefore viable for measuring oxidation states of transition metals in battery electrolyte solutions.

Beyond the BMS shift, additional shifting of select peaks can be induced by coordination to paramagnetic metals *via* the hyperfine shift, which has both contact and pseudocontact

Table 1  ${}^1\text{H}$  peak shifts and corresponding  $\text{Mn}^{2+}$  molar magnetic susceptibilities. The peak shift indicates difference between chemical shifts of (i) electrolyte solution + 0.1 M  $\text{NEt}_4\text{BF}_4$  and (ii) the same solution with 5 mM  $\text{Mn}(\text{TFSI})_2$  added

|                                  | EC     | EMC ethyl<br>$\text{CH}_2$ | EMC<br>methyl | EMC<br>ethyl<br>$\text{CH}_3$ | $\text{NEt}_4\text{BF}_4$<br>$\text{CH}_2$ |
|----------------------------------|--------|----------------------------|---------------|-------------------------------|--------------------------------------------|
| $\Delta\delta$ (ppm)             | 0.339  | 0.326                      | 0.325         | 0.316                         | 0.315                                      |
| $\chi_M$ (mL mol <sup>-1</sup> ) | 0.0162 | 0.0155                     | 0.0155        | 0.0151                        | 0.0150                                     |

(dipolar) components. To compare the reliability of susceptibilities obtained from EC and EMC peak shifts,  $\text{NEt}_4\text{BF}_4$  was added to the electrolyte solution, since  $\text{NEt}_4^+$  is not expected to coordinate to transition metal cations, and  $\chi_M$  was measured for dissolved  $\text{Mn}(\text{TFSI})_2$ . Table 1 shows magnetic data obtained from comparing diamagnetic and  $\text{Mn}^{2+}$ -containing electrolyte solutions, both with 0.1 M  $\text{NEt}_4\text{BF}_4$ .

Peak shifts in Table 1 follow EC > EMC ethyl  $\text{CH}_2$  ~ EMC methyl > EMC ethyl  $\text{CH}_3$  ~  $\text{NEt}_4\text{BF}_4$   $\text{CH}_2$ . The shifts are similar, suggesting all resonances can be used to extract  $\chi_M$ . However, the EMC ethyl  $\text{CH}_3$  resonance shows the smallest  $\Delta\delta$  on addition of  $\text{Mn}^{2+}$  (presumably because it is furthest from the O atoms involved in metal coordination): this shift therefore provides the most accurate  $\chi_M$  among the solvent peaks. Notably, because the EMC ethyl  $\text{CH}_3$  shift is similar to the  $\text{NEt}_4\text{BF}_4$   $\text{CH}_2$  shift, this shows  $\text{NEt}_4\text{BF}_4$  addition permits measurement of the BMS shift. The addition of a non-coordinating agent may be beneficial in solutions where solvent peaks are affected by significant hyperfine shifts.

The major contribution to the  $\text{Mn}^{2+}$  hyperfine shifts likely arises from a contact shift, as high-spin  $\text{d}^5 \text{Mn}^{2+}$  is isotropic<sup>28</sup> so pseudocontact shifts are not possible.<sup>14</sup> This is in contrast to  $\text{Ni}^{2+}$ ,  $\text{Cu}^{2+}$ , and high-spin  $\text{Co}^{2+}$ , which may have anisotropic magnetic susceptibilities and may undergo pseudocontact and contact shifts. Peak shifts may also occur due to differences in metal coordination and binding environments within the electrolytes, as observed for  $\text{Li}^+$  coordination in carbonate electrolyte solutions, where C and O sites (probed by  ${}^{13}\text{C}$  and  ${}^{17}\text{O}$  NMR) nearer to coordinated  $\text{Li}^+$  undergo larger changes in chemical shift on addition of  $\text{LiPF}_6$ .<sup>31,32</sup> Whether arising from a contact or deshielding effect, the larger shift for EC in Table 1 may indicate that  $\text{Mn}^{2+}$  preferentially coordinates to EC, consistent with previous computational work.<sup>33</sup>

The EMC ethyl  $\text{CH}_3$  peak shift was then used to characterise Mn and Ni dissolved from  $\text{LiMn}_2\text{O}_4$ ,  $\text{LiNiO}_2$ , and  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  (Fig. 4). Cathode powders were stored with electrolyte and 0.1 vol% water (to generate HF) at 60 °C. ( $\text{Mn}^{2+}$  dissolution was also observed from  $\text{LiMn}_2\text{O}_4$  stored without added water, ESI,† Fig. S2.) Concentrations from ICP-OES (see below/ESI,†) were used to predict the total  $\chi$  using the calibration in Fig. 1(i).

In all cases, measurements of samples with dissolved Mn and Ni from cathode materials match measurements of samples with dissolved  $\text{Mn}(\text{TFSI})_2$  and  $\text{Ni}(\text{TFSI})_2$ . The predictions would be inaccurate if the solutions contained dissolved metals with different oxidation states; *e.g.*,  $\text{Mn}^{2+}$  has  $\mu_s = 5.92 \mu_{\text{B}}$  and  $\mu_{\text{eff}} \approx 5.65\text{--}6.10 \mu_{\text{B}}$ ,<sup>30</sup> while  $\text{Mn}^{3+}$  has  $\mu_s = 4.90 \mu_{\text{B}}$  and

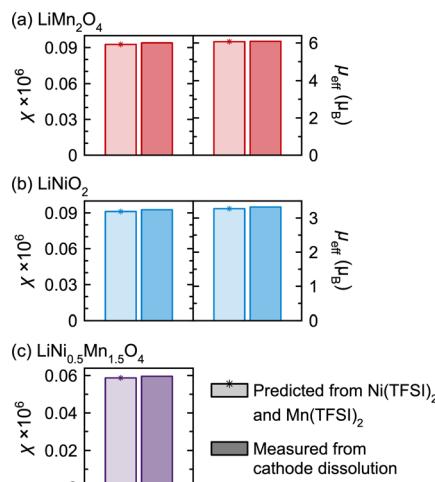


Fig. 4  $\chi$  and  $\mu_{\text{eff}}$  for ions dissolved from (a)  $\text{LiMn}_2\text{O}_4$ , (b)  $\text{LiNiO}_2$ , and (c)  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$ . Predicted arises from  $\text{Mn}(\text{TFSI})_2$  and  $\text{Ni}(\text{TFSI})_2$   $\chi_M$  values multiplied by ICP-OES concentrations; predicted  $\mu_{\text{eff}}$  values are those reported in Fig. 3 for  $\text{Mn}(\text{TFSI})_2$  and  $\text{Ni}(\text{TFSI})_2$ .

$\mu_{\text{eff}} \approx 4.90\text{--}5.00 \mu_B$ .<sup>30</sup> The BMS shift therefore shows that the metals dissolved from  $\text{LiMn}_2\text{O}_4$ ,  $\text{LiNiO}_2$ , and  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  are exclusively  $\text{Mn}^{2+}$  and  $\text{Ni}^{2+}$ . We note, however, that results may differ depending on the dissolution mechanism (for instance, in a full cell, a high-voltage mechanism may cause dissolution of different species).

If one species is dissolved and  $\chi_M$  is known, concentration may also be determined (eqn (1)). For  $\text{LiMn}_2\text{O}_4$  and  $\text{LiNiO}_2$ , the peak shift predicts 6.11 mM  $\text{Mn}^{2+}$  and 20.31 mM  $\text{Ni}^{2+}$ . ICP-OES of the NMR samples showed  $6.03 \pm 0.04$  mM Mn and  $19.98 \pm 0.07$  mM Ni, respectively. (For  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  ICP-OES, see ESI†).

In short, we show the oxidation states of dissolved transition metals in battery electrolyte solutions can be determined from simple solution NMR spectra. Even in cases where one metal oxidation state is diamagnetic (e.g.,  $\text{Cu}^+$ ,  $\text{Co}^{3+}$ ), the fraction of paramagnetic dissolution can be determined by using the susceptibility of the paramagnetic ion (e.g.,  $\text{Cu}^{2+}$ ,  $\text{Co}^{2+}$ ) and solving for its concentration; any remaining metal concentration is then diamagnetic. This accessible method may be applied to any paramagnetic species, making it suitable for lithium-ion and beyond-lithium systems using any liquid electrolyte chemistry. Knowledge of dissolved oxidation states may clarify dissolution mechanisms and dictate strategies adopted to mitigate battery degradation.

This work was funded by the Faraday Institution (grant number FIRG001), the Natural Sciences and Engineering Research Council of Canada, and the Royal Society. JA thanks Evan Zhao for helpful discussions.

## Conflicts of interest

There are no conflicts to declare.

## References

- O. C. Harris, S. E. Lee, C. Lees and M. Tang, *J. Phys. Energy*, 2020, 2(3), 032002.
- C. Zhan, T. Wu, J. Lu and K. Amine, *Energy Environ. Sci.*, 2018, 11(2), 243.
- J. A. Gilbert, I. A. Shkrob and D. P. Abraham, *J. Electrochem. Soc.*, 2017, 164(2), A389.
- W. Choi and A. Manthiram, *J. Electrochem. Soc.*, 2006, 153(9), A1760.
- Y. Terada, Y. Nishiwaki, I. Nakai and F. Nishikawa, *J. Power Sources*, 2001, 97–98, 420.
- R. Sahore, D. C. O'Hanlon, A. Tornheim, C.-W. Lee, J. C. Garcia, H. Iddir, M. Balasubramanian and I. Bloom, *J. Electrochem. Soc.*, 2020, 167(2), 020513.
- A. Banerjee, Y. Shilina, B. Ziv, J. M. Ziegelbauer, S. Luski, D. Aurbach and I. C. Halalay, *J. Am. Chem. Soc.*, 2017, 139(5), 1738.
- Z. Li, A. D. Pauric, G. R. Goward, T. J. Fuller, J. M. Ziegelbauer, M. P. Balogh and I. C. Halalay, *J. Power Sources*, 2014, 272, 1134.
- G. Zhou, X. Sun, Q.-H. Li, X. Wang, J.-N. Zhang, W. Yang, X. Yu, R. Xiao and H. Li, *J. Phys. Chem. Lett.*, 2020, 11(8), 3051.
- J. Wandt, A. Freiberg, R. Thomas, Y. Gorlin, A. Siebel, R. Jung, H. A. Gasteiger and M. Tromp, *J. Mater. Chem. A*, 2016, 4(47), 18300.
- D. Huang, C. Engtrakul, S. Nanayakkara, D. W. Mulder, S.-D. Han, M. Zhou, H. Luo and R. C. Tenent, *ACS Appl. Mater. Interfaces*, 2021, 13(10), 11930.
- Y. Shilina, B. Ziv, A. Meir, A. Banerjee, S. Ruthstein, S. Luski, D. Aurbach and I. C. Halalay, *Anal. Chem.*, 2016, 88(8), 4440.
- R. Benedek, *J. Phys. Chem. C*, 2017, 121(40), 22049.
- I. Bertini; C. Luchinat; G. Parigi and E. Ravera *NMR of Paramagnetic Molecules: Applications to Metallobiomolecules and Models*, Elsevier, 2016.
- EPR Spectroscopy: Fundamentals and Methods*, ed. Goldfarb, D., Stoll, S., John Wiley & Sons, Chichester, UK, 2018.
- L. Hanf, J. Henschel, M. Diehl, M. Winter and S. Nowak, *Electrophoresis*, 2020, 41(9), 697–704.
- L. Hanf, M. Diehl, L.-S. Kemper, M. Winter and S. Nowak, *Electrophoresis*, 2020, 41(18–19), 1549–1556.
- L. Hanf, M. Diehl, L.-S. Kemper, M. Winter and S. Nowak, *Electrophoresis*, 2020, 41(18–19), 1568–1575.
- D. H. Jang, Y.-J. Shin and S. M. Oh, Dissolution of Spinel Oxides and Capacity Losses in 4 V Li/Li<sub>x</sub>Mn<sub>2</sub>O<sub>4</sub> Cells, *J. Electrochem. Soc.*, 1996, 143(7), 2204–2211.
- L.-F. Wang, C.-C. Ou, K. A. Striebel and J.-S. Chen, *J. Electrochem. Soc.*, 2003, 150(7), A905–A911.
- J. Wang, M. M. Islam and S. W. Donne, *Electrochim. Acta*, 2021, 386, 138366.
- R. Jung, F. Linsenmann, R. Thomas, J. Wandt, S. Solchenbach, F. Maglia, C. Stinner, M. Tromp and H. A. Gasteiger, *J. Electrochem. Soc.*, 2019, 166(2), A378–A389.
- S. Komaba, N. Kumagai and Y. Kataoka, *Electrochim. Acta*, 2002, 47(8), 1229–1239.
- T. Joshi, K. Eom, G. Yushin and T. F. Fuller, *J. Electrochem. Soc.*, 2014, 161(12), A1915–A1921.
- M. Koltypin, D. Aurbach, L. Nazar and B. Ellis, *Electrochim. Solid-State Lett.*, 2006, 10(2), A40.
- D. F. Evans, *J. Chem. Soc.*, 1959, 2003.
- C. Piguet, *J. Chem. Educ.*, 1997, 74(7), 815.
- S. F. A. Kettle, *Coordination Compounds*, Thomas Nelson and Sons, London, 1969.
- K. Burger, *Coordination Chemistry: Experimental Methods*, The Butterworth Group, London, 1973.
- B. N. Figgis and J. Lewis. The Magnetochemistry of Complex Compounds, *In Modern Coordination Chemistry: Principles and Methods*, Interscience Publishers, New York, 1960.
- X. Bogle, R. Vazquez, S. Greenbaum, A. W. von Cresce and K. Xu, *J. Phys. Chem. Lett.*, 2013, 4(10), 1664.
- L. Yang, A. Xiao and B. L. Lucht, *J. Mol. Liq.*, 2010, 154(2), 131.
- C. Wang, L. Xing, J. Vatamanu, Z. Chen, G. Lan, W. Li and K. Xu, *Nat. Commun.*, 2019, 10(1), 1.