



Cite this: *Green Chem.*, 2023, **25**, 6677

# CO<sub>2</sub>-assisted hydrolytic hydrogenation of cellulose and cellulose-based waste into sorbitol over commercial Ru/C†

Daniele Polidoro,<sup>a</sup> Giancarmelo Stamilla,<sup>a</sup> Matteo Feltracco,<sup>b,c</sup> Andrea Gambaro,<sup>b,c</sup> Alvis Perosa<sup>\*a</sup> and Maurizio Selva<sup>\*a</sup>

A single-step protocol was developed for the hydrolytic hydrogenation of microcrystalline cellulose into sorbitol over commercial carbon-supported Ru, in the presence of gaseous CO<sub>2</sub> as an acid source and molecular hydrogen as a reductant. Under these conditions, cellulose was first hydrolysed to glucose by reversibly formed carbonic acid in water and then instantaneously hydrogenated on Ru/C. By tuning the reaction parameters, such as temperature, time and the relative pressure of CO<sub>2</sub> and hydrogen gas, cellulose was fully converted at 220 °C in 18 h under 30 and 40 bar of H<sub>2</sub> and CO<sub>2</sub>, respectively, with a sorbitol yield of 81%. Blank experiments revealed that without a catalyst and hydrogen, the reaction exhibited <5% conversion and glucose was the only detected product when the reaction was performed under CO<sub>2</sub> pressure. XRD measurements on CO<sub>2</sub>-treated cellulose surprisingly revealed no noticeable changes in the crystallinity index (<10% with respect to microcrystalline cellulose), suggesting that hydrolytic hydrogenation took place on crystalline, not amorphous, cellulose. Furthermore, not only several cellulosic feedstocks, including filter paper, cotton wool, and cotton fiber, but also typical cellulose-based wastes such as a cardboard pizza box were also tested and under the optimized conditions sorbitol was obtained with yields ranging from 56% up to 72% in all cases. No less significant was the Ru/C catalyst stability, which could be recycled at least six times without any noticeable activity loss.

Received 26th May 2023,  
Accepted 27th July 2023  
DOI: 10.1039/d3gc01813j

[rsc.li/greenchem](http://rsc.li/greenchem)

## Introduction

The depletion of fossil feedstocks and the enormous environmental issues posed by their combustion and chemical manipulation are among the most pressing concerns of our society, to which the scientific/industrial community is responding through massive investments in the research of new strategies for a sustainable economy aimed at the conversion/valorisation of biomass into biofuels, renewable molecules and bio-based materials.<sup>1–4</sup> In this context, given its abundance and its reduced impact on the food chain, lignocellulose (LC) is perhaps the best alternative to fossil resources,<sup>5–7</sup> and even more specifically, cellulose, the major component of LC, is the most promising biopolymer for the

synthesis of a variety of chemicals.<sup>8</sup> Among them, sorbitol and its derivatives have widespread applications as dispersing agents, humectants in pharmaceuticals, low-calorie sweeteners, cosmetics and textiles.<sup>9,10–13</sup> Sorbitol is also one of the ten building block chemicals obtainable from cellulosic resources listed as strategic by the US Department of Energy.<sup>14</sup>

The synthesis of sorbitol from cellulose is generally performed *via* a two-step reaction that includes the acid-catalysed hydrolysis of cellulose to glucose followed by the hydrogenation of glucose to sorbitol over metal catalysts (Scheme 1).<sup>15</sup>

Even though the robust crystalline structure of cellulose makes its hydrolytic breakdown to glucose still a challenge, many reaction protocols have been developed over the years.<sup>8</sup> Homogeneous catalysts such as H<sub>2</sub>SO<sub>4</sub> and HCl have been extensively employed for this purpose. The use of strong liquid acids, however, is not sustainable from an environmental standpoint and suffers from serious drawbacks such as low selectivity, difficult product separation, corrosion and the need for acid recovery.<sup>16–18</sup>

As an alternative, several heterogeneous (acid) catalysts have been proposed for the direct conversion of cellulose into polyols.<sup>19–22</sup> Due to the vast body of literature in this area, only a selection of representative works are commented on here. In


<sup>a</sup>Department of Molecular Sciences and Nanosystems, Ca' Foscari University of Venice, Via Torino 155, 30175 – Venezia Mestre, Italy. E-mail: [selva@unive.it](mailto:selva@unive.it)

<sup>b</sup>Institute of Polar Sciences-CNR, Via Torino 155, 30175 – Venezia Mestre, Italy

<sup>c</sup>Department of Environmental Sciences, Informatics and Statistics, Ca' Foscari University of Venice, Via Torino 155, 30175 – Venezia Mestre, Italy

†Electronic supplementary information (ESI) available: HPAEC-MS quantification protocol and product analysis. See DOI: <https://doi.org/10.1039/d3gc01813j>



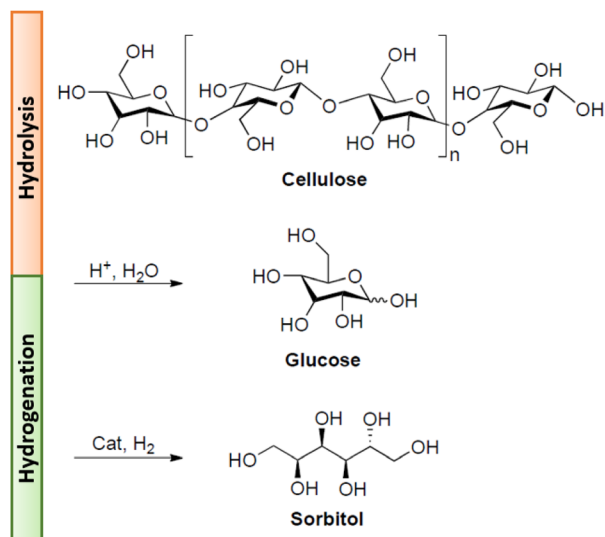

**Scheme 1** Two-step catalytic cellulose conversion into sorbitol, via hydrolysis and hydrogenation.

a first seminal study, Fukuoka and Dhepe described the hydrolytic hydrogenation of cellulose using different metal-based catalysts of which Pt/ $\gamma$ - $\text{Al}_2\text{O}_3$  showed the best performance with a production of sorbitol and mannitol in 25% and 6% yields, respectively.<sup>23</sup> Subsequent studies highlighted that Ru-based catalysts, even commercial ones, were probably the best option for biomass and biomass-derived compounds processing through reductive protocols,<sup>24–26</sup> including the conversion of cellulose into sorbitol, not only because they displayed good activity and selectivity, but also due to their competitive costs since Ru was available at a far lower price (*ca.* ~4%) compared to other metals such as Au and Pt of comparable activity.<sup>27</sup> Luo *et al.* reported that at 245 °C and  $p\text{H}_2 = 60$  bar, in the presence of carbon-supported ruthenium (Ru/C), a high conversion of cellulose was achieved (86%) with a 30% sorbitol yield,<sup>28</sup> though the high temperature caused both a partial degradation of glucose<sup>29</sup> and the hydrogenolysis of sorbitol.<sup>30</sup> Several Ru catalysts supported on acidic carriers such as sulfonated carbon,<sup>6</sup> phosphate,<sup>9</sup> and molecular sieves<sup>31</sup> allowed significant improvements by making the reaction possible at lower temperatures and pressures (<200 °C, 30–50 bar  $\text{H}_2$ ) and with a higher sorbitol yield of up to 71%.<sup>6</sup> Notwithstanding this, the process was slow due to the moderate acidity of the support that brought about a low hydrolysis rate. More performant catalysts were obtained using acid–Ru binary systems where the ratio of acidity to reduction activity could be adjusted: for example, heteropolyacids coupled with Ru/C could effectively improve cellulose conversion, giving a mixture of sorbitol and mannitol in a 68% yield in only 1 h, at 180 °C under 50 bar  $\text{H}_2$ .<sup>29</sup> The poor water solubility of heteropolyacids, however, made difficult the catalyst handling/recovery, thereby hampering any large-scale applications of the procedure. To improve the reusability of the solid acid, zirconium phosphate (ZrP) instead of heteropolyacids was considered, in

combination with Ru/C. This system was apparently highly active, affording an 85% yield of C6 alcohol in 2.5 h, at 190 °C and 50 bar  $\text{H}_2$ .<sup>32</sup> However, it required an acidic pre-treatment of cellulose to reduce its crystallinity; otherwise, the rate-determining hydrolysis step was problematic.<sup>8,33,34</sup> Deng *et al.* reported that the crystallinity of cellulose could be decreased by treating it with phosphoric acid. After this preliminary step, a 69% sorbitol yield was reached *via* hydrolytic hydrogenation catalysed by Ru/CNT (carbon nanotubes) at 185 °C and  $p\text{H}_2 = 50$  bar.<sup>35</sup> Mechanochemical treatments were also evaluated to reduce the crystallinity index of cellulose, especially by ball-milling. A comparative analysis demonstrated that a catalytic mixture of Ru/C and  $\text{H}_4\text{SiW}_{12}\text{O}_{40}$  allowed an 85% and a 36% yield of sugar alcohols starting from ball-milled cellulose and pristine microcrystalline cellulose, respectively.<sup>29</sup> In another work by Pereira *et al.*, a conversion close to 90% with 80% selectivity to sorbitol was reported by ball-milling Ru/C and cellulose together, at 205 °C under 50 bar  $\text{H}_2$  in 1 h.<sup>36</sup>

Whichever the approach, the use of acids, both as solids and even more so as liquids, always implies concerns related to safety, corrosion (especially at high temperatures and pressures), and disposal. Therefore, the design of more sustainable and low-environmental-impact protocols for the direct conversion of cellulose into sorbitol remains a highly desirable target of a modern biorefinery.

The use of  $\text{CO}_2$  may represent a further attractive choice to generate weakly acidic aqueous solutions. This has been proposed and used in several strategies for biomass conversion including pre-treatments of cellulose,<sup>37</sup> rice straw,<sup>38</sup> corn stover,<sup>39</sup> and agroindustrial residues.<sup>40</sup> In particular, it has been demonstrated that the yield of sugars can be significantly improved by introducing  $\text{CO}_2$  during lignocellulose hydrolysis in hot water,<sup>17</sup> thereby confirming the potential of  $\text{CO}_2$ -assisted hydrolysis as a green technology for biomass upgrading.

In this work, the combination of wet  $\text{CO}_2$  as an acid source and molecular hydrogen as a reductant was investigated for the hydrolytic/hydrogenation of microcrystalline cellulose into sorbitol, in the presence of commercial 5% Ru/C. By tuning the reaction parameters, such as temperature, time and pressure, cellulose was fully converted at 220 °C in 18 h under 30 and 40 bar of  $\text{H}_2$  and  $\text{CO}_2$ , respectively, allowing sorbitol formation in 81% yield. To extend the scope, available and cheap cellulose feedstocks, such as filter paper, cotton wool, cotton fiber and a cardboard pizza box were also evaluated as starting materials and a sorbitol yield ranging from 56% to 72% was achieved. Remarkably, the catalytic activity of Ru/C was not altered by the reaction environment during the re-cycling tests for at least six consecutive runs.

## Results and discussion

### Catalyst and acidity

As mentioned above, supported Ru-based systems are among the preferred systems for the hydrogenation of sugars. In this work, with the aim of designing a protocol as easily accessible



as possible, commercial 5% Ru/C (lot #MKBW5890 V) was exclusively used. This catalyst has been characterized for its structural, morphological, and acidic properties in recent papers by our group.<sup>13,41–43</sup> Moreover, to cope with the need for an acidic environment that is crucial for the hydrolysis of cellulose to glucose, the use of pressurised CO<sub>2</sub> able to generate weakly acidic aqueous solutions by the formation of carbonic acid was considered to avoid any issues related to more conventional acids, either liquids or solids.<sup>44</sup> It was known that at 25 °C, the pH of the aqueous solution decreased to about 2.83 when CO<sub>2</sub> was added (70 bar),<sup>45</sup> but more importantly, the acidity was reversible since carbonic acid was (almost) completely removed by venting CO<sub>2</sub> from the reactor. This simple operation did not involve solvent discharge or additional treatments, and (weak) H<sub>2</sub>CO<sub>3</sub> strongly limited any corrosion issues.<sup>17,46,47</sup> Last but not least, CO<sub>2</sub> is nontoxic, and as a by-product of biorefinery processes for fuels and chemicals, it was available at almost no cost.<sup>46</sup>

### CO<sub>2</sub>-assisted hydrolysis of D-maltose into glucose

Exploratory tests were performed to investigate the use of wet CO<sub>2</sub> by employing D-(+)-maltose as a model compound. The CO<sub>2</sub>-assisted hydrolysis of maltose to glucose was studied (Scheme 2).

Experiments were carried out in a stainless-steel autoclave in which an aqueous solution of maltose (maltose: 100 mg; H<sub>2</sub>O: 5 mL) was allowed to react in the presence of CO<sub>2</sub>. The effects of temperature (*T*), time (*t*) and CO<sub>2</sub> pressure (*p*) were investigated through three series of tests by varying the following parameters: (i) *T* in the range 25–150 °C at constant CO<sub>2</sub> pressure (40 bar) and time *t* = 2 h; (ii) time in the range 2–15 h


at constant pressure (40 bar) and temperature (150 °C); and (iii) *p* in the range 5–40 bar, at constant temperature (150 °C) and time (12 h). Maltose conversion and glucose selectivity were determined by HPAEC-MS. All the reported reactions were run in duplicate to ensure reproducibility: unless otherwise specified, conversions and selectivity differed by less than 5% from one test to another. The results are shown in Fig. 1.

No maltose conversion was observed at *p*CO<sub>2</sub> = 40 bar in 2 h in the temperature range 25–100 °C; however, increasing *T* from 120 to 150 °C prompted a gradual increase in the conversion of maltose from 7% to 35%, respectively (Fig. 1a). No products other than glucose, which was obtained in >99% selectivity, were observed under these conditions. Having set 150 °C as the operative temperature to continue this investigation, the effect of time was explored (Fig. 1b). An increase in the reaction time caused an increase in maltose conversion, which became quantitative after 12 h. A small, but not negligible, amount of fructose (1–2%) due to the isomerization of glucose was also detected.<sup>48</sup> No further increase in conversion and selectivity was observed by extending the reaction time to 15 h. This allowed us to set *T* = 150 °C and *t* = 12 h as the conditions to study the effect of CO<sub>2</sub> pressure (Fig. 1c). Notably, high maltose conversion (*ca.* 68–70%) was achieved even at the lowest investigated CO<sub>2</sub> pressure (5 bar), but the reaction became quantitative with excellent glucose selectivity (98–99%) only at 40 bar. A blank experiment was performed at 150 °C for 12 h in the absence of CO<sub>2</sub>. The reaction reached only 27% maltose conversion into glucose, thereby confirming the crucial role of the acidity provided by carbonic acid. The limited extent of the hydrolysis process observed without CO<sub>2</sub> was due to the thermal instability of the β-O-4 glycosidic bond.<sup>49,50</sup>

In summary, parametric analysis showed that the CO<sub>2</sub>-assisted hydrolysis of maltose was strictly dependent on the reaction conditions: however, 98–99% glucose selectivity was obtained with quantitative maltose conversion, at 150 °C, under 40 bar CO<sub>2</sub> for 12 h.

### CO<sub>2</sub>-assisted hydrolysis/hydrogenation of D-maltose into sorbitol

An initial experiment aimed at exploring the direct conversion of maltose into sorbitol was designed under the best con-

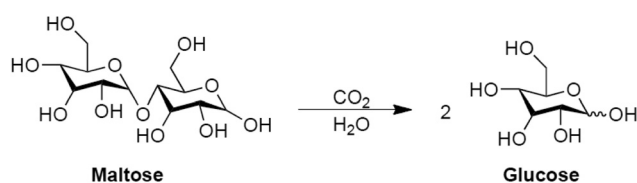

Scheme 2 CO<sub>2</sub>-assisted hydrolysis of D-maltose.

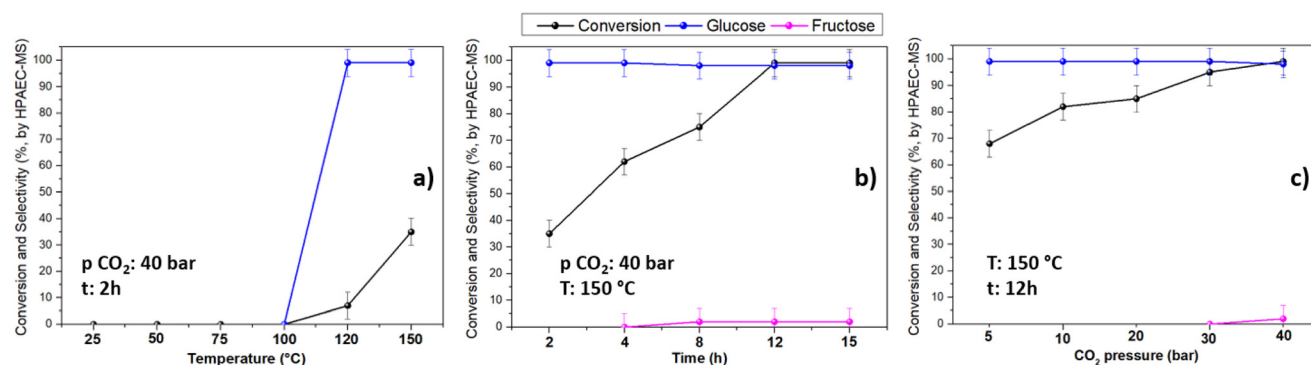


Fig. 1 Effects of (a) temperature; (b) time and (c) CO<sub>2</sub> pressure on the hydrolysis of D-maltose. Reaction conditions: maltose (100 mg) and H<sub>2</sub>O (5 mL). Conversion and selectivity were determined by HPAEC-MS.




ditions observed for maltose hydrolysis (maltose: 100 mg, H<sub>2</sub>O: 5 mL, 150 °C, 40 bar CO<sub>2</sub>, 12 h) with the addition of Ru/C (50 mg) as a hydrogenation catalyst and hydrogen (30 bar). The final pressure was given by  $p_{\text{H}_2} + p_{\text{CO}_2}$  at room temperature, *i.e.* 70 bar. The reaction allowed a quantitative conversion of maltose into a mixture of maltitol (24%) and sorbitol (76%), respectively. Given this promising result, further tests were carried out by varying both the reaction time and the temperature. The results are shown in Fig. 2.

At 150 °C, the prolongation of the reaction from 12, to 15, 18 and 24 h induced a gradual increase in sorbitol selectivity, up to 87%, at the expense of maltitol (Fig. 2a). The desired process was further favoured by slightly increasing the reaction temperature, from 150 to 170 °C: at quantitative conversion, sorbitol was obtained with an excellent 96% selectivity (Fig. 2b). Last but not least, the formation of C<sub>4</sub>–C<sub>5</sub> polyols (derived from hydrogenolysis reactions) during maltose hydrolysis/hydrogenation was never detected by HPAEC-MS.

In principle, different reaction pathways could be hypothesized for the conversion of maltose into sorbitol (Scheme 3). Maltose could be first hydrolysed to glucose, which could be further hydrogenated into sorbitol (pathway A, top); alternatively, the direct hydrogenation of maltose could provide maltitol (pathway B, bottom), followed by its hydrolysis to yield sorbitol and glucose in equimolar amounts. Finally, hydrolysis/hydrogenation of maltose could take place simultaneously to provide sorbitol (pathway C, centre). The results of Fig. 2 clearly highlighted that the catalytic hydrogenation of maltose to maltitol was faster than the hydrolysis reaction, confirming that the conversion of maltose into sorbitol proceeded *via* pathway B.

Moreover, while complete maltose hydrolysis to glucose took place under the standard conditions of 150 °C, 40 bar CO<sub>2</sub>, 12 h (Fig. 1), complete maltitol hydrolysis was slower and

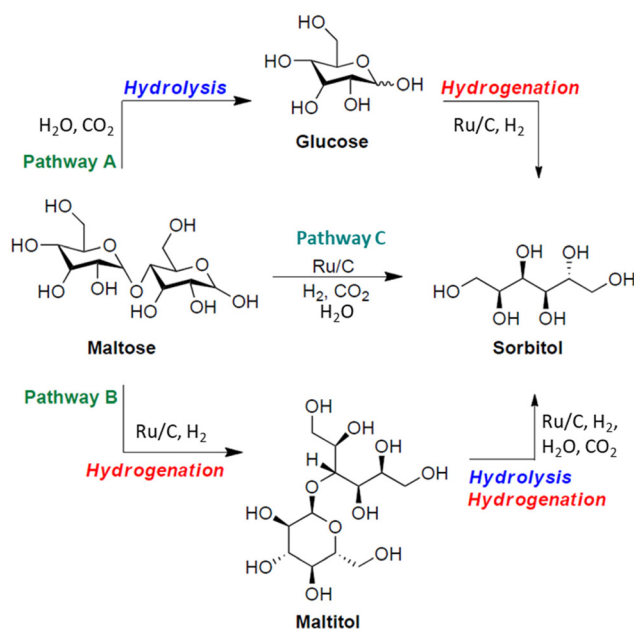


**Scheme 3** Reaction pathways A–C for the CO<sub>2</sub>-assisted hydrogenation of D-maltose into sorbitol.

required harsher conditions (170 °C) and a longer time (24 h) with 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub>. To better understand the reasons for the different behaviour, we first assumed that the presence of 30 bar H<sub>2</sub> played a role in the hydrolysis kinetics of maltitol. In fact, when maltitol was set to react without H<sub>2</sub> under the standard conditions observed for maltose hydrolysis (150 °C, 40 bar CO<sub>2</sub>, 12 h), glucose and sorbitol were achieved much faster with almost equal selectivity (48% and 52%, respectively) at 97% maltitol conversion, seemingly indicating that the presence of H<sub>2</sub> from the preceding reduction step slowed the reaction. An experiment with He in place of H<sub>2</sub> under the standard maltitol hydrolysis conditions (150 °C, 40 bar CO<sub>2</sub>, 12 h and 30 bar He) also showed a lower maltitol conversion (83%) with the glucose/sorbitol ratio remaining unaltered. Both experiments seemed to indicate that the CO<sub>2</sub>-assisted hydrolysis was slower in the presence of additional pressure (H<sub>2</sub> or He). However, since the addition of H<sub>2</sub> or He does not affect the partial pressure of CO<sub>2</sub>, and the pH of the solution presumably remains constant as it depends on CO<sub>2</sub> concentration and thus its partial pressure, the reason for a slower hydrolysis rate does not seem ascribable to a change in pH. The explanation for this behaviour is still unclear and is currently under investigation in our lab.

#### CO<sub>2</sub>-assisted hydrolysis/hydrogenation of cellulose into sorbitol

Based on the results obtained for the CO<sub>2</sub>-assisted hydrolytic hydrogenation of maltose, the next step was to apply the reaction to more complex substrates starting from cellulose. A suspension of microcrystalline cellulose (100 mg) in 5 mL of H<sub>2</sub>O was set to react under 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub> for 24 h, in the presence of Ru/C (50 mg). Different temperatures in the range

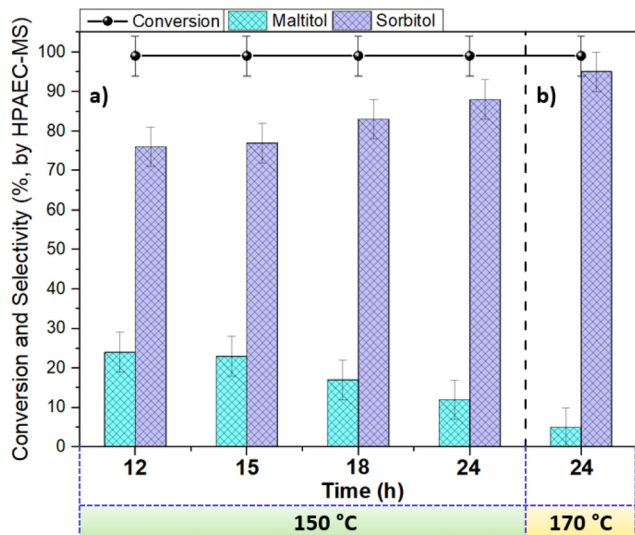

**Fig. 2** Effects of (a) time and (b) temperature on the CO<sub>2</sub>-assisted hydrogenation of maltose into sorbitol. Reaction conditions: maltose (100 mg), H<sub>2</sub>O (5 mL), 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, and Ru/C (50 mg). Conversion and selectivity were determined by HPAEC-MS.





150–250 °C were explored. Cellulose conversion was determined gravimetrically by the difference in weight of cellulose employed in the reaction and the solid recovered after the reaction, taking into consideration also the weight of the solid catalyst. The yield of water-soluble polyols such as sorbitol, mannitol and C<sub>4</sub>–C<sub>5</sub> sugar alcohols was determined by HPAEC-MS (a detailed HPAEC-MS quantification protocol is reported in the ESI section†). The results are reported in Table 1.

At the lower temperature of 150 °C, the conversion of cellulose reached 32%, but the observed products, which included sorbitol, mannitol (as an isomerization product) and a mixture of C<sub>4</sub>–C<sub>5</sub> polyols (hydrogenolysis products such as erythritol, xylitol and arabitol), were obtained in poor, if not negligible, yields of 7%, 2% and <1%, respectively (entry 1). This result was ascribed to the formation of water-soluble oligomers which could not be detected by HPAEC-MS. An increase in the reaction temperature from 150 to 180 and 200 °C improved the conversion to >99%, and considerably favoured the formation of sorbitol which was achieved in up to 67% yield (entries 2 and 3). The concurrent formation of small amounts of mannitol (4%) and C<sub>4</sub>–C<sub>5</sub> polyols (5%) was also observed.


Finally, the yield of sorbitol was further increased to 81% at 220 °C (entry 4), one of the best results reported so far for this reaction. Raising the *T* to 250 °C, however, brought about an increase in hydrolysis products (C<sub>4</sub>–C<sub>5</sub> sugar alcohols) which were obtained in a 26% yield at the expense of sorbitol (54%, entry 5).

In summary, the hydrolytic hydrogenation protocol proved highly efficient in the conversion of cellulose into sorbitol, using CO<sub>2</sub> as an acid precursor and molecular hydrogen as a reductant. Sorbitol was obtained with the highest yield of 81% at 220 °C, under 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub> for 24 h. The formation of hydrogenolysis products such as erythritol, xylitol and arabitol (not exceeding 7% yield) was also observed.

As mentioned in the Introduction section, acidic pre-treatments are often employed to reduce the crystallinity of cellulose and increase its reactivity.<sup>35</sup> To shed light on this aspect under the conditions explored in this work, the effect of the CO<sub>2</sub> acidity on the crystalline structure of cellulose was investi-

gated. Experiments were carried out in 5 mL H<sub>2</sub>O, at 220 °C and for 18 h, in the absence of Ru/C, under a variety of conditions by treating microcrystalline cellulose: (i) as such, without CO<sub>2</sub>; (ii) under 40 bar CO<sub>2</sub>; (iii) under 30 bar H<sub>2</sub> and (iv) under 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub> (conditions of the CO<sub>2</sub>-assisted hydrolytic hydrogenation of cellulose). The crystallinity index of the solid recovered at the end of each test was then measured by XRD. The results are reported in Fig. 3.

Quite unexpectedly, XRD profiles differed by less than 10% from one sample to another and compared to pristine microcrystalline cellulose (crystallinity index of *ca.* 85%). Indeed, in all profiles of Fig. 4(a–e), the strongest peak at  $2\theta = 22.6^\circ$ , which originated from the cellulose crystalline plane (002), indicated that the degree of crystallinity of microcrystalline cellulose was substantially preserved regardless of the presence of CO<sub>2</sub>. Additionally, no cellulose conversion (<5%) was observed when reactions were carried out in the absence of

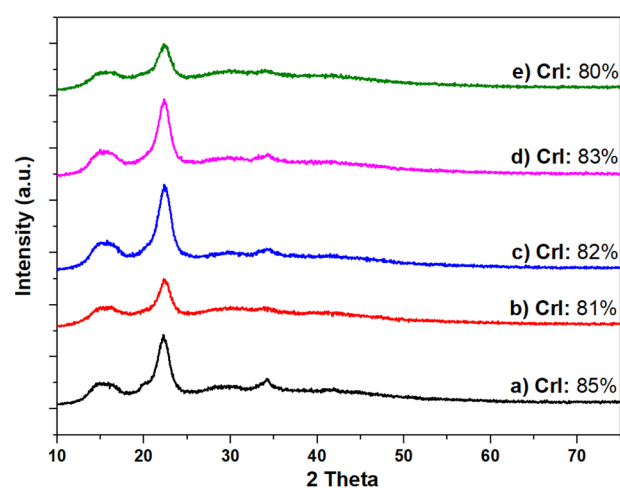



**Fig. 3** XRD profiles of (a) pristine microcrystalline cellulose, (b) microcrystalline cellulose after 18 h at 200 °C, (c) microcrystalline cellulose after 18 h at 200 °C under 40 bar CO<sub>2</sub>, (d) microcrystalline cellulose after 18 h at 200 °C under 30 bar H<sub>2</sub> and (e) microcrystalline cellulose after 18 h at 200 °C under 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub>.

**Table 1** CO<sub>2</sub>-assisted hydrolysis/hydrogenation of cellulose into sorbitol

Entry	Temperature (°C)	Cellulose conversion (%)	Yield (%)		
			Sorbitol	Mannitol	C <sub>4</sub> –C <sub>5</sub> polyols
1	150	32	7	2	<1
2	180	50	41	2	2
3	200	>99	67	4	5
4	220	>99	81	4	7
5	250	>99	54	3	26

Reaction conditions: cellulose (100 mg), Ru/C (50 mg), H<sub>2</sub>O (5 mL), 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, and 24 h. Yield (mass%) was determined by HPAEC-MS.



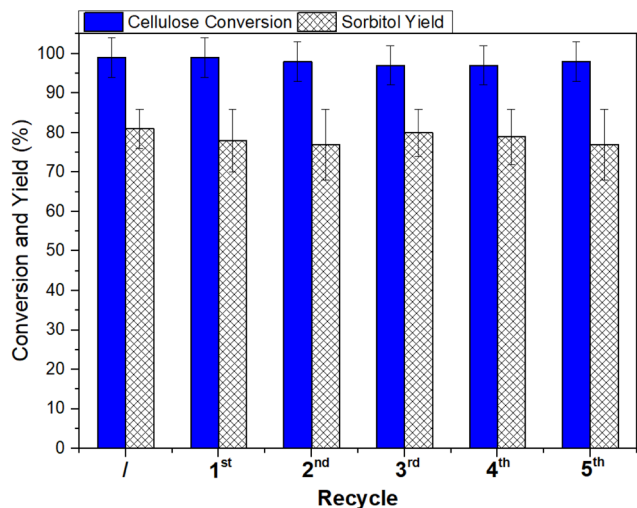

**Fig. 4** Ru/C recycling in the CO<sub>2</sub>-assisted hydrogenation of cellulose into sorbitol. Reaction conditions: cellulose (100 mg), Ru/C (50 mg), H<sub>2</sub>O (5 mL), 220 °C, 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, and 24 h. Yield was determined by HPAEC-MS.

CO<sub>2</sub> (profiles b and c), while in contrast, in the presence of CO<sub>2</sub>, with or without additional hydrogen (d and e), measurements revealed *ca.* 67–70% cellulose conversion and glucose was the only detected product from HPAEC-MS. In other words, CO<sub>2</sub> favoured the hydrolytic breakdown of the biopolymer, but in the unreacted cellulose, CO<sub>2</sub> was apparently unable to modify the domains where the polymer chains were aligned with each other, against the hypothesis that CO<sub>2</sub> acidity worked by reducing the crystallinity.

### Catalyst recycling

The cost of the catalyst in a liquid-phase reaction may represent up to a third of the total cost of the process, implying that its loss by leaching or other reasons is critical, and its recovery and reuse are crucial.<sup>52</sup> The stability and reusability of Ru/C were therefore investigated by designing recycling experiments under the conditions described in Table 1, entry 4 (cellulose: 100 mg, Ru/C: 50 mg, H<sub>2</sub>O: 5 mL, 220 °C, 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, 24 h). Once the first reaction was completed, the catalyst was filtered, washed with distilled water (30 mL) and dried overnight. During the recycling tests, the catalyst amount differed by less than 5% from one test to another and fresh Ru/C was added during the recycling tests to maintain the original catalyst/substrate ratio. The recovered catalyst was added to fresh microcrystalline cellulose (100 mg), water (5 mL) and the appropriate amount of Ru/C and a new reaction was started. The recycling procedure was repeated six times, and the whole set of reactions was run twice to ensure reproducibility. The results are illustrated in Fig. 4. Both the cellulose conversion and the sorbitol yield remained steady at 97–99% and 77–81%, respectively, during the six runs, thereby demonstrating that the overall performance of Ru/C was not altered over time by the reaction environment during the recycling tests and by the washing/restoring procedures.

### CO<sub>2</sub>-assisted hydrolysis/hydrogenation of cellulose feedstock/waste into sorbitol

Other real-world cellulose sources were explored to investigate the applicability and scalability of the CO<sub>2</sub>-assisted hydrolysis/hydrogenation protocol. In this scope, cheap and readily available cellulosic feedstocks, including filter paper, cotton wool, and cotton fiber, and common cellulose-based wastes such as a pizza carton made of cardboard were selected. A mixture of finely ground cellulose feedstock (100 mg, size <1 mm), Ru/C (50 mg) and H<sub>2</sub>O (5 mL) was set to react at 220 °C for 24 h, under 40 bar CO<sub>2</sub> and 30 bar H<sub>2</sub>. The conversion and yield were determined by the same method described previously. The results are summarized in Table 2.

First, the commonly employed laboratory filter paper was tested. Such a starting material was fully converted, allowing sorbitol formation in 62% yield with the concurrent formation of mannitol (3%) and, if compared with microcrystalline cellulose, a higher amount of C<sub>4</sub>–C<sub>5</sub> polyols (21%). A remarkable improvement in sorbitol yield was observed when cotton wool and cotton fibers were tested. In these cases, sorbitol was obtained in 71% and 72% yields, respectively, with an almost equal amount of mannitol (5% and 4% respectively) and C<sub>4</sub>–C<sub>5</sub> polyols (7% and 6%, respectively), while the conversion remained stable and quantitative in both cases. The pizza carton made of cardboard was also completely converted, with a sorbitol yield of 56%, while mannitol and C<sub>4</sub>–C<sub>5</sub> polyols were observed in 6% and 13% yields, respectively. Overall, these results not only confirmed that the investigated reductive protocol was effective for the direct conversion of cellulose into sorbitol, but they also proved that the process was successfully applied to a wide range of cellulose feedstocks.

### Comparison of the CO<sub>2</sub>-assisted hydrolytic hydrogenation of cellulose to literature results

A comparative assessment of the reported CO<sub>2</sub>-assisted protocol for the conversion of cellulose into sorbitol against other methods was carried out by selecting some of the most representative works from the vast body of literature in this area. To make the analysis as consistent as possible, batch liquid phase methods that used Ru/C catalysts and pristine microcrystalline cellulose were considered. Table 3 shows the results.

**Table 2** CO<sub>2</sub>-assisted hydrolysis/hydrogenation of different cellulose feedstocks

Entry	Cellulose feedstock	Conversion (%)	Yield (%)		
			Sorbitol	Mannitol	C <sub>4</sub> –C <sub>5</sub> polyols
1	Filter paper	>99	62	3	21
2	Cotton wool	>99	71	5	7
3	Cotton fiber	>99	72	4	6
4	Pizza carton	>99	56	6	13

Reaction conditions: cellulose feedstock (100 mg), Ru/C (50 mg), H<sub>2</sub>O (5 mL), 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, and 24 h. Yield (mass%) was determined by HPAEC-MS.



**Table 3** Comparative assessment of methods for the conversion of cellulose into sorbitol

Entry	Catalyst	Acid	Experimental conditions ( <i>T</i> , <i>p</i> H <sub>2</sub> , <i>t</i> )	Cellulose conversion (%)	Sorbitol yield (%)	Ref.
1	Ru/C	—	245, 60, 0.5	86	35	28
2	Ru/C	H <sub>4</sub> SiW <sub>12</sub> O <sub>40</sub>	180, 50, 1	99	68	29
3	Ru/C	ZrP <sup>a</sup>	190, 50, 3	99	64 <sup>b</sup>	32
4	Ru/C	CO <sub>2</sub> <sup>c</sup>	220, 30, 24	>99	81	This work

<sup>a</sup> ZrP: zirconium phosphate. <sup>b</sup> Yield referred to C<sub>6</sub>-alditols. <sup>c</sup> 40 bar CO<sub>2</sub>.

An efficient cellulose conversion into polyols by combination of hydrolysis using H<sup>+</sup> ions, reversibly formed *in situ* in hot water, with instantaneous hydrogenation over Ru/C was reported by Liu<sup>28</sup> (entry 1). Upon considering the absence of any additional acid source and the reduced reaction time (0.5 h) as sustainable and environmentally friendly aspects, the higher temperature of 245 °C promoted the formation of a mixture of C<sub>1</sub>–C<sub>5</sub> products and the final sorbitol yield was low (*ca.* 34–35%). However, the addition of heteropolyacids (entry 2) not only allowed us to reduce the reaction temperature to 180 °C but also helped us to increase the sorbitol yield to 68% after 1 h.<sup>29</sup> However, as mentioned in Introduction, the low solubility of heteropolyacids in aqueous solutions made their handling/recovery difficult. To solve this problem, zirconium phosphate (ZrP) instead of heteropolyacids was employed as a solid acid source<sup>32</sup> (entry 3). With this system, by tuning the reaction parameters, 64% yield of a mixture of C<sub>6</sub>-alditols was achieved after 3 h at 190 °C under 50 bar H<sub>2</sub>. On the other hand, employing CO<sub>2</sub> as an acid precursor, sorbitol was obtained in 81% yield with quantitative cellulose conversion. To the best of our knowledge, this is the best result reported for this transformation. Among the green advantages of the reported procedure, it is worth noting that (i) carbonic acid is sufficiently acidic for the complete glycolysis of cellulose, and even more importantly, its formation is reversible by simply venting the reactor, ensuring a lack of product contamination, limiting corrosion and improving safety compared to using conventional liquid or solid acids; (ii) the catalyst (Ru/C) can be recycled at least six times without significant activity loss; and (iii) the protocol proved effective not only for microcrystalline cellulose but also for other cellulosic feedstocks, including filter paper, cotton wool, and cotton fiber as well as typical cellulose wastes such as a pizza carton. Based on this evidence, the proposed protocol paves the way for the design of innovative and simple methods for the recovery and valorisation of any cellulose-based feedstocks, including waste, to produce sorbitol in what is a typical circular economy approach.

## Experimental section

### Materials and equipment

D-(+)-Maltose (>99%), microcrystalline cellulose, and 5% Ru/C (lot #MKBW5890V) were commercially available compounds sourced from Sigma-Aldrich. If not otherwise specified,

reagents were employed without further purification. Water was of Milli-Q grade. H<sub>2</sub> gas was purchased from SIAD, Italy. Quantitative analyses were performed by high-pressure anion exchange chromatography and ion chromatography (Thermo Scientific™ Dionex™ ICS-5000) coupled to a single quadrupole mass spectrometer (Thermo Scientific™ MSQ Plus™) (HPAEC-MS). The crystallinity index of cellulose samples was investigated by X-ray diffraction (XRD) using a D8 Advance Bruker® AXS diffractometer, with Cu Kα radiation as the X-ray source, coupled to a Lynxeye detector, and monitoring the 2θ within 10–80° at a rate of 0.08° min<sup>−1</sup>. All reactions were performed in duplicate to verify reproducibility.

### Typical CO<sub>2</sub>-assisted hydrogenation experiments

Experiments were performed in a 25 mL tubular reactor made from borosilicate glass (Pyrex), which was charged with microcrystalline cellulose (100 mg), 5% Ru/C (50 mg) and water (5 mL). The vessel was placed in a jacketed stainless-steel autoclave equipped with a manometer and two needle valves, and pressurised with hydrogen to 30 bar and CO<sub>2</sub> to 40 bar (the final pressure was given by *p*H<sub>2</sub> + *p*CO<sub>2</sub> at room temperature). The autoclave was then heated by oil circulation at *T* = 150–250 °C, and the mixture was kept under magnetic stirring at a rate of 1500 rpm. After the desired reaction time (24 h), the autoclave was cooled to room temperature and gently purged. The catalyst (Ru/C) was filtered on PTFE (0.2 μm) and the product solutions were analysed by HPAEC-MS.

### Catalyst recycling

The recycling/reuse of the catalyst was investigated after the CO<sub>2</sub>-assisted hydrogenation of cellulose under the following reaction conditions: cellulose (100 mg), Ru/C (50 mg), H<sub>2</sub>O (5 mL), 220 °C, 40 bar CO<sub>2</sub>, 30 bar H<sub>2</sub>, for 24 h. Once the first reaction was complete, the catalyst was filtered on PTFE, washed with H<sub>2</sub>O (30 mL) and dried overnight. The recovered catalyst was added with fresh cellulose (100 mg) and H<sub>2</sub>O (5 mL) and a new reaction was started. The overall sequence was repeated for six subsequent runs (five recycles), and each reaction was run twice to ensure reproducibility.

### Product analysis

Cellulose conversion (*C*<sub>cellulose</sub>, %) was determined based on the weight of cellulose utilized in the reaction (*m*<sub>cellulose,0</sub>) and the solid recovered after the reaction, taking into consideration



the fraction of the solid catalyst in the remainder with  $m_{\text{cellulose}}$   
 $= m_{\text{recovered solid}} - m_{\text{catalyst}}$  (eqn (1)).

$$C_{\text{cellulose}}\% = \frac{m_{\text{cellulose},0} - m_{\text{cellulose}}}{m_{\text{cellulose},0}} \times 100 \quad (1)$$

Product analysis and quantification were performed according to a validated method by Barbaro *et al.*<sup>53</sup> A detailed protocol is reported in the ESI section.†

### Crystallinity index determination

The crystallinity index (CrI) was calculated using the XRD peak height method,<sup>51</sup> according to the following equation:

$$\text{CrI}\% = \frac{I_{002} - I_{\text{AM}}}{I_{002}} \times 100$$

where  $I_{002}$  is the maximum intensity of the (002) lattice diffraction ( $2\theta = 22.6^\circ$ ) and  $I_{\text{AM}}$  is the intensity diffraction at  $2\theta: 18^\circ$ .  $I_{002}$  represents both crystalline and amorphous cellulose, whereas  $I_{\text{AM}}$  represents amorphous cellulose only.

## Conclusions

The herein reported study demonstrates the efficiency and robustness of a one-step  $\text{CO}_2$ -assisted hydrolytic hydrogenation protocol for the conversion of cellulose into sorbitol. The use of maltose as a model substrate has been tested in the first part of the investigation to prove the role of  $\text{CO}_2$  in the hydrolytic breakdown of the glycosidic bond: at 150–170 °C, in an aqueous solution pressurised with  $\text{CO}_2$  (30 bar), the weak acidity due to carbonic acid is enough to make the glycolysis proceed to completion with the formation of glucose. Importantly, the reversible formation of carbonic acid, which is removed by venting the reactor, improves the safety and environmental impact of the procedure, and strongly limits any corrosion issues. Next, when Ru/C and hydrogen are added to the reaction system, a selectivity of up to 96% is achieved towards the product, sorbitol, derived from a tandem sequence: the hydrolysis of maltose followed by the hydrogenation of glucose. By tuning the reaction parameters, the protocol is also equally effective in the conversion of microcrystalline cellulose into sorbitol. At 220 °C, 40 bar  $\text{CO}_2$  and 30 bar  $\text{H}_2$  for 24 h, cellulose is fully converted, with a sorbitol yield of 81%, one of the best results reported to date for this transformation. Six consecutive recycling tests in the  $\text{CO}_2$ -assisted hydrolysis/hydrogenation of cellulose prove the excellent stability of Ru/C that can be easily recovered by filtration from the reaction medium. Finally, the scope of the reaction can be extended to other largely available cellulose sources, including filter paper, cotton wool, cotton fiber and pizza cartons made from cardboard: sorbitol is obtained in good-to-excellent yields ranging from 56% to 72% in all cases. Overall, this study not only proves the concept of combining two selective processes of hydrolysis and hydrogenation to achieve an added-value polyol such as sorbitol straight from cellulose, through a single-batch process, but it also paves the way for

the design of innovative and simple methods for the recovery and valorisation of any cellulose-based feedstocks including waste.

## Author contributions

D.P.: conceptualization, investigation, methodology, and writing – original draft preparation; G.S.: investigation and analytical methodology; M.F.: investigation and analytical methodology; M.F.: investigation and analytical methodology; A.G.: supervision and funding acquisition; A.P.: conceptualization, supervision, writing – reviewing and funding acquisition; M.S.: conceptualization, supervision, writing – reviewing and editing, and funding acquisition.

## Conflicts of interest


The authors declare no conflict of interest.

## Acknowledgements

Ca' Foscari Università di Venezia is gratefully acknowledged for its valuable support during the development of this work.

## References

- 1 A. M. Ruppert, K. Weinberg and R. Palkovits, *Angew. Chem., Int. Ed.*, 2012, **51**, 2564–2601.
- 2 D. M. Alonso, S. G. Wettstein and J. A. Dumesic, *Chem. Soc. Rev.*, 2012, **41**, 8075–8098.
- 3 Q. Di, Y. Wang, A. Zanobetti, Y. Wang, P. Koutrakis, C. Choirat, F. Dominici and J. D. Schwartz, *N. Engl. J. Med.*, 2017, **376**, 2513–2522.
- 4 D. R. Gentner, S. H. Jathar, T. D. Gordon, R. Bahreini, D. A. Day, I. El Haddad, P. L. Hayes, S. M. Pieber, S. M. Platt, J. De Gouw, A. H. Goldstein, R. A. Harley, J. L. Jimenez, A. S. H. Prévôt and A. L. Robinson, *Environ. Sci. Technol.*, 2017, **51**, 1074–1093.
- 5 C. H. Zhou, X. Xia, C. X. Lin, D. S. Tong and J. Beltramini, *Chem. Soc. Rev.*, 2011, **40**, 5588–5617.
- 6 J. W. Han and H. Lee, *Catal. Commun.*, 2012, **19**, 115–118.
- 7 Y. Zhou, G. Chen, Z. Long and J. Wang, *RSC Adv.*, 2014, **4**, 42092–42113.
- 8 M. Yabushita, H. Kobayashi and A. Fukuoka, *Appl. Catal., B*, 2014, **145**, 1–9.
- 9 J. Xi, Y. Zhang, Q. Xia, X. Liu, J. Ren, G. Lu and Y. Wang, *Appl. Catal., A*, 2013, **459**, 52–58.
- 10 R. Gérardy, D. P. Debecker, J. Estager, P. Luis and J. C. M. Monbaliu, *Chem. Rev.*, 2020, **120**, 7219–7347.
- 11 F. Brandi and M. Al-Naji, *ChemSusChem*, 2022, **15**, e202102525.
- 12 J. Zhang, J. B. Li, S. B. Wu and Y. Liu, *Ind. Eng. Chem. Res.*, 2013, **52**, 11799–11815.





- 13 D. Polidoro, A. Perosa, E. Barbaro, M. Feltracco, E. Argiriadis and M. Selva, *ACS Sustainable Chem. Eng.*, 2022, **10**, 2844–2858.
- 14 J. J. Bozell and G. R. Petersen, *Green Chem.*, 2010, **12**, 539–555.
- 15 L. S. Ribeiro, J. J. Delgado, J. J. M. Órfão and M. F. R. Pereira, *Appl. Catal., B*, 2017, **217**, 265–274.
- 16 X. Wang, L. Meng, F. Wu, Y. Jiang, L. Wang and X. Mu, *Green Chem.*, 2012, **14**, 758–765.
- 17 J. Liang, X. Chen, L. Wang, X. Wei, H. Wang, S. Lu and Y. Li, *Bioresour. Technol.*, 2017, **228**, 147–155.
- 18 K. Wu, Y. Wu, Y. Chen, H. Chen, J. Wang and M. Yang, *ChemSusChem*, 2016, **9**, 1355–1385.
- 19 A. Negoii, K. Triantafyllidis, V. I. Parvulescu and S. M. Coman, *Catal. Today*, 2014, **223**, 122–128.
- 20 H. Kobayashi, Y. Ito, T. Komanoya, Y. Hosaka, P. L. Dhepe, K. Kasai, K. Hara and A. Fukuoka, *Green Chem.*, 2011, **13**, 326–333.
- 21 P. L. Dhepe and A. Fukuoka, *ChemSusChem*, 2008, **1**, 969–975.
- 22 M. Kåldström, N. Kumar and D. Y. Murzin, *Catal. Today*, 2011, **167**, 91–95.
- 23 A. Fukuoka and P. L. Dhepe, *Angew. Chem., Int. Ed.*, 2006, **45**, 5161–5163.
- 24 S. Gyergyek, D. Lisjak, M. Beković, M. Grilc, B. Likozar, M. Nečemer and D. Makovec, *Nanomaterials*, 2020, **10**, 1–9.
- 25 R. Šivec, M. Huš, B. Likozar and M. Grilc, *Chem. Eng. J.*, 2022, **436**, 32–40.
- 26 R. Šivec, M. Grilc, M. Huš and B. Likozar, *Ind. Eng. Chem. Res.*, 2019, **58**, 16018–16032.
- 27 D. Zhao, T. Su, Y. Wang, R. S. Varma and C. Len, *Mol. Catal.*, 2020, **495**, 111133.
- 28 C. Luo, S. Wang and H. Liu, *Angew. Chem., Int. Ed.*, 2007, **46**, 7636–7639.
- 29 J. Geboers, S. Van De Vyver, K. Carpentier, K. De Blochouse, P. Jacobs and B. Sels, *Chem. Commun.*, 2010, **46**, 3577–3579.
- 30 G. Liang, L. He, H. Cheng, W. Li, X. Li, C. Zhang, Y. Yu and F. Zhao, *J. Catal.*, 2014, **309**, 468–476.
- 31 J. Zhang, L. Lin, J. Zhang and J. Shi, *Carbohydr. Res.*, 2011, **346**, 1327–1332.
- 32 Y. Liao, Q. Liu, T. Wang, J. Long, L. Ma and Q. Zhang, *Green Chem.*, 2014, **16**, 3305–3312.
- 33 V. B. Agbor, N. Cicek, R. Sparling, A. Berlin and D. B. Levin, *Biotechnol. Adv.*, 2011, **29**, 675–685.
- 34 P. Yang, H. Kobayashi and A. Fukuoka, *Chin. J. Catal.*, 2011, **32**, 716–722.
- 35 W. Deng, X. Tan, W. Fang, Q. Zhang and Y. Wang, *Catal. Lett.*, 2009, **133**, 167–174.
- 36 L. S. Ribeiro, J. J. M. Órfão and M. F. R. Pereira, *Green Chem.*, 2015, **17**, 2973–2980.
- 37 M. Muin, A. Adachi, M. Inoue, T. Yoshimura and K. Tsunoda, *J. Wood Sci.*, 2003, **49**, 65–72.
- 38 M. Gao, F. Xu, S. Li, X. Ji, S. Chen and D. Zhang, *Biosyst. Eng.*, 2010, **106**, 470–475.
- 39 N. Narayanaswamy, A. Faik, D. J. Goetz and T. Gu, *Bioresour. Technol.*, 2011, **102**, 6995–7000.
- 40 A. R. C. Morais, A. C. Mata and R. Bogel-Lukasik, *Green Chem.*, 2014, **16**, 4312–4322.
- 41 A. Bellè, T. Tabanelli, G. Fiorani, A. Perosa, F. Cavani and M. Selva, *ChemSusChem*, 2019, **12**, 3343–3354.
- 42 D. Polidoro, A. Perosa and M. Selva, *ChemSusChem*, 2022, **15**, e202201059.
- 43 A. Bellè, K. Kusada, H. Kitagawa, A. Perosa, L. Castoldi, D. Polidoro and M. Selva, *Catal. Sci. Technol.*, 2022, **12**, 259–272.
- 44 C. Schacht, C. Zetzl and G. Brunner, *J. Supercrit. Fluids*, 2008, **46**, 299–321.
- 45 K. L. Toews, R. M. Shroll, C. M. Wai and N. G. Smart, *Anal. Chem.*, 1995, **67**, 4040–4043.
- 46 L. V. A. Gurgel, M. T. B. Pimenta and A. A. da S. Curvelo, *Ind. Crops Prod.*, 2014, **57**, 141–149.
- 47 H. Lv, L. Yan, M. Zhang, Z. Geng, M. Ren and Y. Sun, *Chem. Eng. Technol.*, 2013, **36**, 1899–1906.
- 48 A. A. Marianou, C. M. Michailof, A. Pineda, E. F. Iliopoulou, K. S. Triantafyllidis and A. A. Lappas, *ChemCatChem*, 2016, **8**, 1100–1110.
- 49 W. Yin, Z. Tang, R. H. Venderbosch, Z. Zhang, C. Cannilla, G. Bonura, F. Frusteri and H. J. Heeres, *ACS Catal.*, 2016, **6**, 4411–4422.
- 50 S. Yamaguchi, S. Fujita, K. Nakajima, S. Yamazoe, J. Yamasaki, T. Mizugaki and T. Mitsudome, *ACS Sustainable Chem. Eng.*, 2021, **9**, 6347–6354.
- 51 S. Park, J. O. Baker, M. E. Himmel, P. A. Parilla and D. K. Johnson, *Biotechnol. Biofuels*, 2010, **3**, 1–10.
- 52 I. Sádaba, M. L. Granados, A. Riisager and E. Taarning, *Green Chem.*, 2015, **17**, 4133–4145.
- 53 E. Barbaro, T. Kirchgeorg, R. Zangrando, M. Vecchiato, R. Piazza, C. Barbante and A. Gambaro, *Atmos. Environ.*, 2015, **118**, 135–144.

