



Cite this: *Nanoscale*, 2023, **15**, 14584

High-efficiency visible-light-driven oxidation of primary C–H bonds in toluene over a CsPbBr_3 perovskite supported by hierarchical TiO_2 nanoflakes†

JIAYU YI,^a SUNZAI KE,^a SUWEI LU,^a BO WENG,^b LIJUAN SHEN,^a XUHUI YANG,^a HUN XUE,^a MIN-QUAN YANG,^a and QINGRONG QIAN,^a

Photocatalytic oxidation of toluene to valuable fine chemicals is of great significance, yet faces challenges in the development of advanced catalysts with both high activity and selectivity for the activation of inert $\text{C}(\text{sp}^3)\text{–H}$ bonds. Halide perovskites with remarkable optoelectronic properties have shown to be prospective photoactive materials, but the bulky structure with a small surface area and severe recombination of photogenerated electron–hole pairs are obstacles to application. Here, we fabricate a hierarchical nanoflower-shaped $\text{CsPbBr}_3/\text{TiO}_2$ heterojunction by assembling CsPbBr_3 nanoparticles on 2D TiO_2 nanoflake subunits. The design significantly downsizes the size of CsPbBr_3 from micrometers to nanometers, and forms a type II heterojunction with intimate interfacial contact between CsPbBr_3 and TiO_2 nanoflakes, thereby accelerating the separation and transfer of photogenerated charges. Moreover, the formed hierarchical heterojunction increases light absorption by refraction and scattering, offers a large surface area and enhances the adsorption of toluene molecules. Consequently, the optimized $\text{CsPbBr}_3/\text{TiO}_2$ exhibits a high performance ($10\,200\ \mu\text{mol g}^{-1}\ \text{h}^{-1}$) for photocatalytic toluene oxidation with high selectivity (85%) for benzaldehyde generation under visible light. The photoactivity is about 20 times higher than that of blank CsPbBr_3 , and is among the best photocatalytic performances reported for selective oxidation of toluene under visible light irradiation.

Received 6th July 2023,
Accepted 4th August 2023

DOI: 10.1039/d3nr03282e
rsc.li/nanoscale

Introduction

The direct oxidation of toluene to high-added-value fine chemicals, such as alcohols and aldehydes, is one of the most important conversions in the chemical industry.^{1–4} However, due to the inertness and high bond dissociation energy (89.8 kcal mol^{–1}) of the $\text{C}(\text{sp}^3)\text{–H}$ bond,⁵ the activation of toluene generally needs to be performed under harsh reaction conditions (high pressure and temperature) and with the assistance of specific metal complexes or aggressive oxidants, which is expensive, energy intensive and causes negative impacts on the environment.^{6–8} Solar-driven photocatalytic aerobic oxidation using molecular O_2 as an oxidant represents a promising method-

ology to overcome these challenges, but the overall photocatalytic performance reported so far is still unsatisfactory due to the lack of desired photocatalysts with broad optical absorption windows, efficient charge separation, and high product selectivity.^{9–11}

Over the past years, halide perovskite materials have triggered wide attention in photocatalysis because of their outstanding optical and electronic properties.^{12–16} High charge carrier mobility, visible light absorption, and tunable band structures enable them to be potential competitors for photocatalytic oxidation of toluene.^{17,18} Nevertheless, single-component halide perovskites typically evolve into bulky aggregates with a large particle size (several to tens of micrometers), which leads to severe bulk recombination of charge carriers and restricts the photoactivity.^{19,20} To tackle this problem, the construction of a heterojunction is an effective strategy. Hybridization of the halide perovskite with preferred substrates not only can prevent the aggregation of the halide perovskite to mediate the bulk recombination of photoexcited electron–hole pairs, but also can establish an interfacial built-in electric field to further facilitate the spatial charge transfer and separation.²¹

Moreover, the catalytic functions of photocatalysts also strongly depend on the nanostructure.^{22,23} To realize high

^aCollege of Environmental and Resource Sciences, College of Carbon Neutral Modern Industry, Fujian Key Laboratory of Pollution Control & Resource Reuse, Fujian Normal University, Fuzhou 350117, P.R. China. E-mail: yangmq@fjnu.edu, cnqrqian@fjnu.edu.cn

^bcMACS, Department of Microbial and Molecular Systems, KU Leuven, Celestijnenlaan 200F, 3001 Leuven, Belgium

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3nr03282e>

photocatalytic performance, the delicate design of a well-defined nanostructure for heterojunction composites is also critical.^{24–27} For diverse structural configurations, 3D hierarchical flower-like nanostructures constructed using 2D nanoflake subunits have demonstrated intrinsic advantages for photocatalysis. Such hierarchical structures can strengthen the light absorption of photocatalysts by multi-light reflection and scattering within the nanoflake subunits, and prohibit the aggregation of 2D nanoflakes to afford a large surface area with abundant active sites.^{28,29} In addition, the nanoflake subunits will greatly shorten the diffusion path of charges, thereby facilitating the separation and transfer of photogenerated charges to the surface for redox reactions.^{30,31} Thus, the development of advanced 2D subunit-assembled hierarchical structures with a heterogeneous junction would be promising for high-efficiency photocatalytic toluene oxidation.

Here, inspired by the above considerations, we design and fabricate a hierarchical nanoflower-shaped $\text{CsPbBr}_3/\text{TiO}_2$ (abbreviated as CPB/TiO₂) heterojunction composed of TiO₂ nanoflake-supported all-inorganic CsPbBr₃ perovskite nanoparticles. Benefiting from the composition and nanostructure engineering, the CPB/TiO₂ heterojunction displays excellent performance for photocatalytic toluene oxidation under the irradiation of visible light. The optimized 20%CPB/TiO₂ heterojunction composite delivers a toluene conversion rate of 10 200 $\mu\text{mol g}^{-1} \text{h}^{-1}$ and a high selectivity of 85% towards benzaldehyde (benzyl alcohol as the main by-product). This performance outperforms most of the state-of the-art catalysts in the literature for visible-light-driven oxidation of toluene. This work provides a new idea by constructing a hierarchical heterojunction structure over halide perovskite materials for high-efficiency photocatalytic toluene conversion.

Experimental section

Materials

Cesium bromide (CsBr, 99.999%), lead bromide (PbBr₂, 99.0%) and tetrahydrofuran (THF) were purchased from Macklin (Shanghai, China). *N,N*-Dimethylformamide (DMF), toluene, tetrabutyl titanate (TBOT), ethanol (EtOH), concentrated hydrochloric acid (HCl, 36%), acetic acid and glycerol were obtained from Sinopharm Chemical Reagent Co., Ltd (Shanghai, China). All chemicals and solvents were used without further purification.

Synthesis of mesoporous hierarchical TiO₂ nanoflowers

Typically, 1.5 g of Pluronic F127 was dispersed in a mixed solvent of 2.4 mL of acetic acid, 3.2 mL of concentrated hydrochloric acid (HCl) and 30 mL of tetrahydrofuran (THF). After vigorously stirring for 20 min, 3.4 mL of tetrabutyl titanate (TBOT) and 0.2 mL of H₂O were added subsequently to obtain a clear primrose yellow solution. After that, the solution was dried in an oven at 45 °C for 24 h to form a light-yellow gel. Then, 1.0 g of the gel was added into 25 mL of ethanol (EtOH) and 5 mL of glycerin under vigorous stirring. After 20 min, the

transparent solution was transferred to a 50 mL Teflon-lined autoclave, heated at 150 °C for 15 h, and then cooled naturally to room temperature. The precipitate was washed with ethanol and dried in an oven at 60 °C.³² Finally, the precipitate was calcined in a muffle furnace at 400 °C for 5 h at a heating rate of 1 °C min⁻¹ to obtain the hierarchical TiO₂ nanoflowers. To synthesize the collapsed TiO₂ without the hierarchical nanoflower structure, the precipitate was calcined in the same muffle furnace at 400 °C for 5 h, but at a heating rate of 5 °C min⁻¹.

Synthesis of $\text{CsPbBr}_3/\text{TiO}_2$ composites and blank CsPbBr_3

$\text{CsPbBr}_3/\text{TiO}_2$ composites were synthesized according to an antisolvent precipitation method at room temperature.³³ Typically, 1 mmol CsBr and 1 mmol PbBr₂ were dissolved in 10 mL of *N,N*-dimethylformamide (DMF) by ultrasonication to form a precursor solution. Meanwhile, 100 mg of TiO₂ was dispersed in 10 mL of DMF and stirred to form a uniform white dispersion. Then a certain amount of the CsPbBr₃ precursor solution was added into the TiO₂ dispersion under ultrasonication. Then, the mixture was added dropwise into 50 mL of toluene and stirred vigorously for 30 min. After that, the solution was centrifuged at 8000 rpm for 3 min. The precipitate was collected and dried in a vacuum oven. A series of $x\%$ $\text{CsPbBr}_3/\text{TiO}_2$ composites were synthesized by changing the volume of the added CsPbBr₃ precursor solution, where x is the mass ratio of CsPbBr₃ in the composite ($x = 10, 20, 30$, and 40). Blank CsPbBr₃ was prepared by the same procedure without the addition of TiO₂.

Characterization

Scanning electron microscopy (SEM) images were captured using a Hitachi 8100. Transmission electron microscopy (TEM) and high-resolution transmission electron microscopy (HRTEM) images were recorded using a JEM-2100F EX microscope at an accelerating voltage of 200 kV. The Brunauer–Emmett–Teller (BET) specific surface area was measured using an N₂ adsorption–desorption instrument (BELSORP-mini II). The X-ray diffraction (XRD) patterns of the catalysts were characterized on a Bruker D8 Advance X-ray diffractometer operated at 40 kV and 40 mA with Cu K α radiation and 2θ ranging from 10° to 80°. The UV-vis diffuse reflectance spectra (DRS) were obtained on a CARY-100 spectrophotometer (Agilent) using 100% BaSO₄ powder as a standard sample. X-ray photoelectron spectroscopy (XPS) spectra were recorded using an X-ray photoelectron spectrometer (Thermo Escalab 250 electron spectrometer) with Al-K α radiation. Raman spectra were obtained using a laser at a wavelength of 785 nm (Thermo Fisher Scientific, DXR 2xi). Photoluminescence (PL) spectra of solid samples were obtained using an RF-5301PC spectrophotometer (Shimadzu, Japan) with a 435 nm excitation wavelength.

Electron paramagnetic resonance (EPR) measurements were performed at room temperature using a MagneTech ESR5000X spectrometer. In general, 10 mg samples were dispersed in a mixed solution of 2 mL of CH₃CN containing 1 mL

of toluene and 2 μ L of 5,5-dimethyl-1-pyrroline-*N*-oxide (DMPO). The suspension was then transferred into a glass capillary. The sealed glass tube was then placed in the microwave cavity of an EPR spectrometer and exposed to a 300 W Xe lamp source (CEL-PF300-T8, Beijing China Education Au-light Co., Ltd) at room temperature.

Photoelectrochemical measurements

The photoelectrochemical analysis was carried out in a conventional three-electrode cell using a Pt plate and an Ag/AgCl electrode as the counter electrode and the reference electrode, respectively. The working electrode was prepared on fluorine-doped tin oxide (FTO) glass that was cleaned by ultrasonication in ethanol for 1 h. Typically, 5 mg of the catalyst was dispersed in 0.5 mL of isopropanol to obtain a slurry. After that, 20 μ L of the slurry was dropped onto FTO with a size of 1 cm^2 and dried in air. The electrochemical impedance spectroscopy (EIS) measurement was performed in an electrolyte of tetrabutylammonium hexafluorophosphate (TBAPF₆) in ethyl acetate (EA). The transient photocurrent was tested in the same electrolyte and a 300 W xenon lamp (CEL-PF300-T8, Beijing China Education Au-light Co., Ltd) equipped with a 420 nm cutoff filter ($\lambda \geq 420$ nm) was used as the light source. Mott–Schottky measurement was performed in an electrolyte of 0.1 M TBAPF₆ in CH₂Cl₂.

Density functional theory (DFT) calculations

DFT calculations were carried out using the Vienna *ab initio* simulation package (VASP) with the projector-augmented-wave (PAW) method.³⁴ The Perdew–Burke–Ernzerhof (PBE) scheme was used for the exchange correlation function, employing the generalized gradient approximation (GGA).³⁵ The electronic wave function was expanded using a plane wave basis with an energy cutoff of 500 eV. The energy convergence criterion was set to 1.0×10^{-5} eV, and the force convergence criterion was set to 0.03 eV \AA^{-1} for each atom. For the CsPbBr₃ (110) and TiO₂ (101) slabs, a $6 \times 3 \times 1$ and $3 \times 9 \times 1$ *k*-point mesh was used, respectively. A 30 \AA vacuum layer along the *z*-direction was used to prevent unintended periodic interactions between adjacent slabs. The CsPbBr₃/TiO₂ heterostructure model consists of two CsPbBr₃ layers and one TiO₂ layer, with a 20 \AA vacuum space along the *z*-direction. To save computing resources, a $1 \times 1 \times 1$ *k*-point mesh was employed for the CsPbBr₃/TiO₂ heterostructure. The van der Waals interactions between TiO₂ and CsPbBr₃ were taken into account using the DFT-D3 correction method.

Photocatalytic activity measurements

All photocatalytic reactions were conducted in a quartz reactor. Typically, 10 mg of the photocatalyst and 1 mL of toluene (9.4 mmol) were dispersed in a reactor containing 2 mL of acetonitrile. The reactor was purged with O₂ for 10 min, and then irradiated with visible light ($\lambda > 420$ nm) using a 300 W xenon lamp (CEL-PF300-T8, Beijing China Education Au-light Co., Ltd). After light irradiation for 2 h, the liquid product was analyzed by gas chromatography (GC-2030, Shimadzu, Japan,

FID detector, nitrogen (N₂) as the carrier gas) after centrifuging the suspension at 10 000 rpm for 3 min.

Results and discussion

Characterization of catalysts

The 3D hierarchical CPB/TiO₂ heterostructure was prepared by a simple anti-solvent precipitation method with the addition of TiO₂ nanoflowers into the precursor solution of CsPbBr₃, as schematically illustrated in Fig. 1a. X-ray diffraction (XRD) was exploited to characterize the crystal structure of blank CsPbBr₃, CPB/TiO₂ composites and TiO₂. As shown in Fig. 1b, the diffraction peaks at 15.1°, 21.5°, 30.7°, 34.4°, and 43.8° can be ascribed to the monoclinic CsPbBr₃ (100), (110), (200), (210) and (220) planes (JCPDS no. 18-0364).^{36–38} In addition, the peaks at 25.3°, 37.7°, 48.0°, 53.8°, 55.0°, and 62.6° can be attributed to the (101), (004), (200), (105), (211), and (204) planes of anatase TiO₂, respectively.³² The XRD patterns of CPB/TiO₂ composites indicate both characteristic peaks of CsPbBr₃ and TiO₂, and the peak intensity of CsPbBr₃ increases as the CsPbBr₃ content increases (Fig. S1†).

Raman spectra were used to further confirm the composition of the synthesized catalysts. As shown in Fig. 1c, the peaks at 151 cm^{-1} (E_g), 403 cm^{-1} (E_g), 523 cm^{-1} (A_{1g} + B_{1g}), and 646 cm^{-1} (E_g) belong to the anatase TiO₂ vibration modes. A new peak of 74 cm^{-1} assigned to the vibrational mode of the [PbBr₆]⁴⁻ octahedron of CsPbBr₃ is observed in the CPB/TiO₂ composite.^{39–41} The characteristic peak of CsPbBr₃ is also enhanced with the increment of the loading amount of CsPbBr₃ (Fig. S2†). This coincides with the XRD analysis, validating the successful preparation of the CPB/TiO₂ composites. Notably, after the growth of CsPbBr₃ on the TiO₂ nanosheets, the Raman peaks of TiO₂ shift to a lower wavenumber compared to that of blank TiO₂. The shift indicates an increase in the bond length and a decrease in the bond energy of the Ti–O bond, which can be attributed to the strong electrostatic interaction between CsPbBr₃ and TiO₂.^{42–45} Fig. 1d shows the UV-vis diffuse reflectance spectroscopy (DRS) analysis of the samples, which is employed to assess the optical absorption properties. It can be seen that the light absorption edge of blank TiO₂ is around 390 nm, denoting its UV light response nature. After integrating with CsPbBr₃, the light absorption of CPB/TiO₂ is extended to approximately 540 nm. Meanwhile, the absorption edge of TiO₂ at 390 nm can also be detected. This should be ascribed to the hybridization of the high weight content of CsPbBr₃ with the TiO₂ support. As such, both absorption features are present in the composite. The greatly extended light absorption enables the visible light excitation of the CPB/TiO₂ composites, which is beneficial for promoting solar energy utilization. With the increase of the CsPbBr₃ content, the visible light absorption of CPB/TiO₂ is also gradually enhanced (Fig. S3†). Moreover, in comparison with blank CsPbBr₃, it is notable that the visible light absorption edge of the hybrid CPB/TiO₂ composite is slightly blue shifted (*ca.* 14 nm). This can be attributed to the quantum size

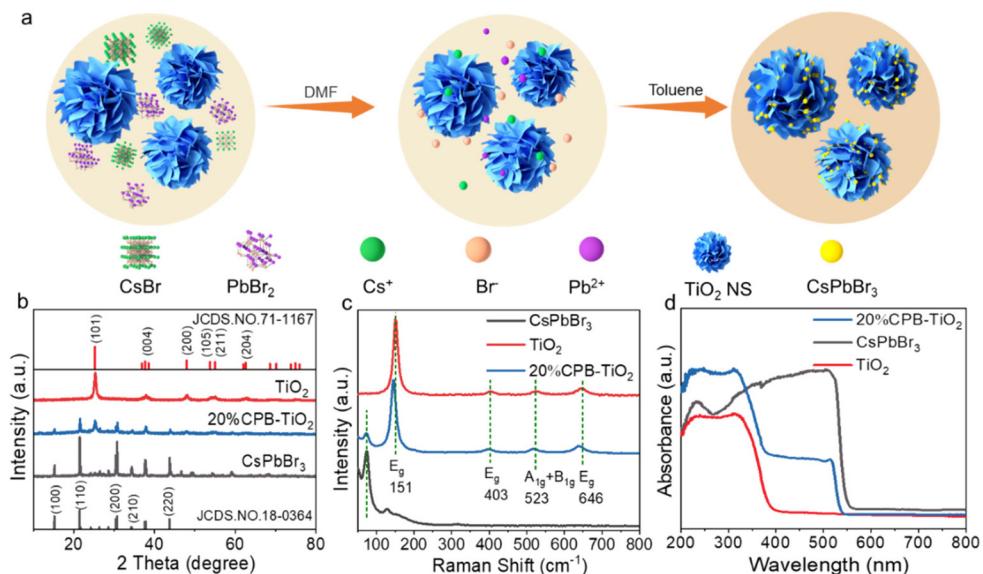


Fig. 1 (a) Schematic diagram of the synthesis of 3D nanoflower-shaped CPB/TiO₂ heterostructure. (b) XRD patterns, (c) Raman spectra, and (d) UV-vis DRS spectra of CsPbBr₃, CPB/TiO₂ and TiO₂.

effect resulting from the smaller size of CsPbBr₃ in the composite. The inference has been demonstrated by the following scanning electron microscopy (SEM) and transmission electron microscopy (TEM) analyses.

As shown in Fig. 2, Fig. S4 and S5,† SEM is firstly utilized to characterize the morphology and microstructure of the CPB/TiO₂, blank TiO₂ and CsPbBr₃ samples. The blank TiO₂ presents a nanoflower shape, which is assembled by vertical nano-

flakes (Fig. S4†). The surface of the nanoflake subunits is clean and smooth. For blank CsPbBr₃, it shows a large particle morphology and the particle sizes range from 0.9 to 2.0 μ m (Fig. S5†). After the construction of the CPB/TiO₂ heterojunction, the TiO₂ nanoflower-shaped structure is maintained (Fig. 2), while the surface of the nanoflake subunits becomes rough due to the *in situ* growth of CsPbBr₃. From Fig. 2b–i, it can be clearly seen that for all the CPB/TiO₂ samples, the sizes

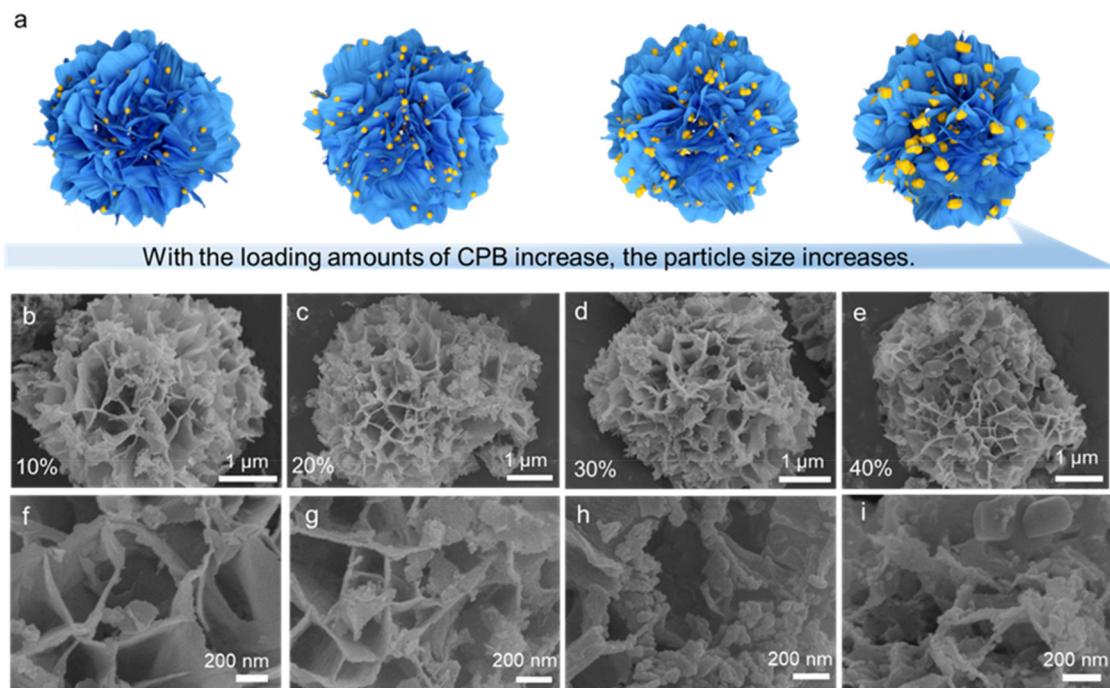


Fig. 2 (a) Schematic and (b–i) SEM images showing the morphology evolution of x% CPB/TiO₂ (where x = 10, 20, 30, and 40) composites.

of the CsPbBr_3 particles in the composites are much smaller than that of blank CsPbBr_3 , indicating that the formation of a heterojunction is beneficial for preventing the aggregation and reducing the size of the CsPbBr_3 halide perovskite. This can be ascribed to the fact that the presence of TiO_2 nanoflowers with nanoflake subunits can act as heterogeneous nucleus sites to facilitate the nucleation and growth of CsPbBr_3 , which generates more seeds and leads to the smaller size of the CsPbBr_3 particles.²⁰ The significantly decreased particle size could greatly promote the exposure of surface active sites and inhibit the charge recombination of CsPbBr_3 under light irradiation. Moreover, it is notable that with the increase of the CsPbBr_3 contents from 10% to 40% in the composites, the particle sizes of CsPbBr_3 are increased, as schematically illustrated in Fig. 2a. This can be attributed to the further growth of CsPbBr_3 at high concentrations.

To further obtain the microscopic structural information of the samples, transmission electron microscopy (TEM) analysis is carried out. Taking 20%CPB/ TiO_2 as an example, the TEM image of the sample (Fig. 3a and b) shows a nanoflake structure of TiO_2 . The surface is rough and densely covered by small CsPbBr_3 nanoparticles. Since the sample for TEM analysis is prepared by strong ultrasonication, the well-defined CsPbBr_3 nanoparticles on the 2D nanoflake surface indicate intimate interfacial contact between the two components. Meanwhile, the intensive coverage of CsPbBr_3 forms a large contact interface with TiO_2 nanoflakes, which is conducive to the migration of charge carriers across the CPB/ TiO_2 heterojunction.⁴⁶ Moreover, nanopores can be observed on the CPB/ TiO_2 , which results from the mesoporous structure of the TiO_2 nanoflakes, as demonstrated by the N_2 adsorption–desorption analysis (Fig. S6†). The high-resolution TEM (HRTEM) image (Fig. 3c) shows distinct lattice fringes of 0.35 nm and 0.41 nm, corresponding to the (101) planes and (110) planes of anatase

TiO_2 and monoclinic CsPbBr_3 , respectively. Furthermore, Fig. 3d shows the corresponding energy dispersive X-ray spectroscopy (EDS) elemental mapping analysis of 20%CPB/ TiO_2 . Cs, Pb, Br, Ti and O elements are uniformly distributed on the nanoflake structure, indicating that CsPbBr_3 and TiO_2 are well combined. The results further verify the formation of CPB/ TiO_2 hybrid composite with intimate interfacial contact. Moreover, in comparison with blank TiO_2 , the 20%CPB/ TiO_2 composite displays a smaller specific surface area (Table S1†), which can be attributed to the fact that the growth of CsPbBr_3 nanoparticles on the surface of TiO_2 may aggregate in the TiO_2 pores. Correspondingly, the total pore volume of 20%CPB/ TiO_2 is also slightly lower than that of blank TiO_2 . The result matches with the SEM measurement.

To study the surface chemical states of the samples, X-ray photoelectron spectroscopy (XPS) has been performed. As shown in Fig. 4a, the presence of Cs, Pb, Br, O and Ti elements can be detected from the XPS survey spectrum of CPB/ TiO_2 . The high-resolution spectrum of Ti 2p shows two peaks of Ti 2p_{3/2} and Ti 2p_{1/2} at 458.5 eV and 464.2 eV (Fig. 4b), which indicates that Ti element mainly exists as Ti^{4+} ions. For the O 1s pattern (Fig. 4c), it can be divided into two peaks, which are attributed to the lattice O (Ti–O) and hydroxyl O (–OH). Fig. S7† shows the fine-scanned Cs 3d XPS spectrum, and the two peaks with binding energies at 724.2 eV and 738.1 eV are assigned to Cs 3d_{5/2} and Cs 3d_{3/2}, indicating that the chemical state of the Cs in the composite is +1. The Pb 4f spectrum in Fig. 4d shows characteristic peaks at 138.0 eV and 142.9 eV, corresponding to Pb 4f_{7/2} and Pb 4f_{5/2} orbitals of Pb^{2+} ion. Moreover, the Br 3d is decomposed into two peaks at 67.9 eV and 68.9 eV, corresponding to the binding energies of Br 3d_{5/2} and 3d_{3/2}, attributed to the presence of Br^- (Fig. 4e). It is worth noting that for the CPB/ TiO_2 composite, the Ti 2p and O

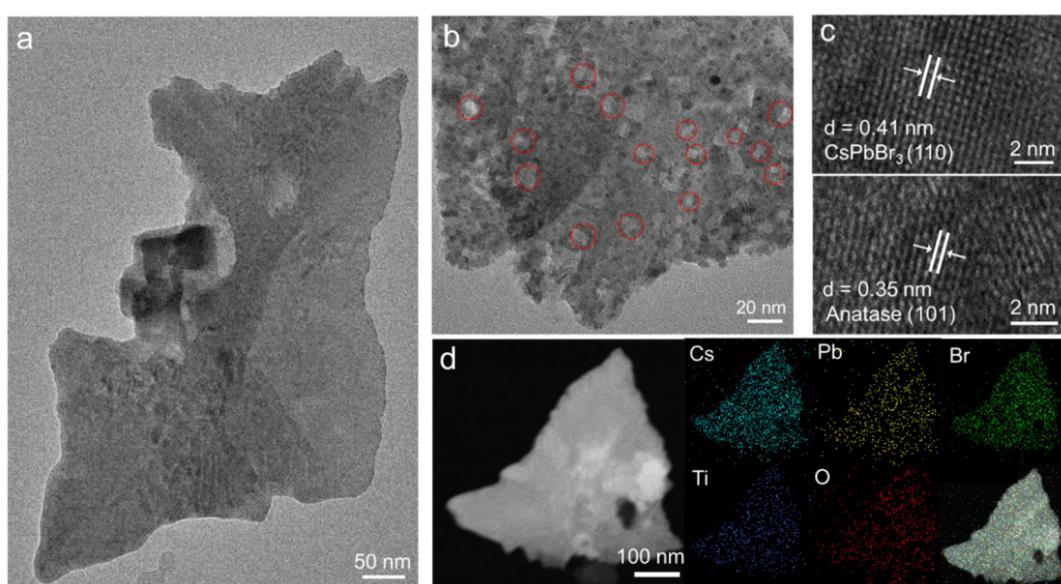


Fig. 3 (a and b) TEM images, (c) HRTEM image, and (d) corresponding EDS elemental mapping images of 20%CPB/ TiO_2 .

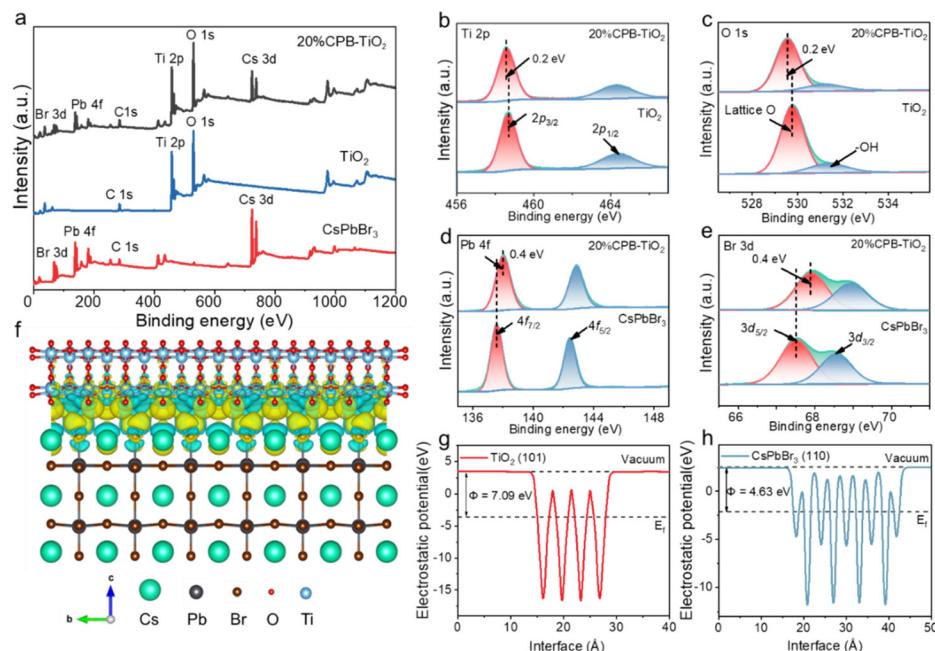


Fig. 4 XPS spectra of CsPbBr_3 , TiO_2 and 20%CPB/ TiO_2 : (a) survey, (b) Ti 2p, (c) O 1s, (d) Pb 4f and (e) Br 3d. (f) Charge density differences in the CPB/ TiO_2 composite. (g and h) The work functions of blank TiO_2 and CsPbBr_3 .

1s peaks show a negative shift of 0.2 eV in comparison with blank TiO_2 (Fig. 4b and c). In contrast, the binding energies of Cs 4d, Pb 4f, and Br 3d in the CPB/ TiO_2 show a positive shift (Fig. 4d and e and S7†), which are higher than those of blank CsPbBr_3 by 0.4 eV. The results verify the strongly interacted interface with electron transfer from the CsPbBr_3 to the TiO_2 nanosheets in the heterostructure, which is in accordance with the Raman analysis. To further clarify the interaction and electron transfer at the interface, density functional theory (DFT) calculations have been carried out. Fig. 4g and h shows the work functions of the TiO_2 (101) and CsPbBr_3 (110) slabs, which are 7.09 eV and 4.63 eV, respectively, corresponding to the Fermi levels (E_f) of -3.61 eV and -2.51 eV (vs. the vacuum level). Due to the lower E_f value of TiO_2 than that of blank CsPbBr_3 , the electrons would be migrated from CsPbBr_3 to TiO_2 at the heterojunction interface until their E_f are aligned. A similar result is obtained from the calculated planar-averaged charge density difference of CPB/ TiO_2 . As shown in Fig. 4f, the light cyan and yellow regions indicate the charge depletion and accumulation area, respectively. The calculation results reveal that the cyan region is mainly on the CsPbBr_3 side, while the yellow region is on the TiO_2 side, further validating the transfer of electrons from CsPbBr_3 to TiO_2 . This is consistent with the XPS analysis results.

Photocatalytic performances

Collectively, the above characterization faithfully verifies the successful fabrication of CPB/ TiO_2 hybrid composites with intimate interfacial contact and strong chemical interaction. The presence of TiO_2 nanoflower with 2D nanoflake subunits greatly inhibits the agglomeration of the halide perovskites,

while CsPbBr_3 extends the light absorption range of TiO_2 . In view of the desired structural and optical properties, the photocatalytic oxidation of toluene over the hybrid CPB/ TiO_2 composites has been tested. A 300 W xenon lamp equipped with a 420 nm cutoff filter is utilized as a visible light source. It is well known that the solvent/reactant ratio has great influence on the oxidation of toluene,^{2,47} and thus, the reaction condition of different acetonitrile/toluene ratio is firstly optimized using 20%CPB/ TiO_2 as an example. As shown in Fig. 5a, as the ratio of toluene increases from 0.3 to 1 mL, the photoactivity of the 20%CPB/ TiO_2 composite gradually increases. The catalyst shows the highest toluene conversion rate of $10\,200\, \mu\text{mol g}^{-1}\, \text{h}^{-1}$ when the volume ratio of acetonitrile solvent and toluene reactant is 2 : 1. The enhanced photoactivity can be attributed to the fact that the increased toluene concentration enhances the reaction possibility between the photogenerated charge carriers and the toluene molecules. However, further increase of toluene to 1.5 mL and 2 mL decreases the conversion rate. This might be ascribed to the excess adsorption of the toluene reactant on the catalyst surface, which would slow down the desorption of the BA and BAD products and suppress the oxidation activity.⁴⁸ Based on the result, the following photoactivity tests of all the other samples are carried out under the optimized condition with a acetonitrile/toluene ratio of 2 : 1.

Fig. 5b shows the visible-light-driven photocatalytic performances of the blank CsPbBr_3 and CPB/ TiO_2 composites with different ratios of CPB for the selective oxidation of toluene. The blank CsPbBr_3 exhibits a low activity with generation rates of $390\, \mu\text{mol g}^{-1}\, \text{h}^{-1}$ for BAD and $130\, \mu\text{mol g}^{-1}\, \text{h}^{-1}$ for BA. The unsatisfactory photocatalytic performance should

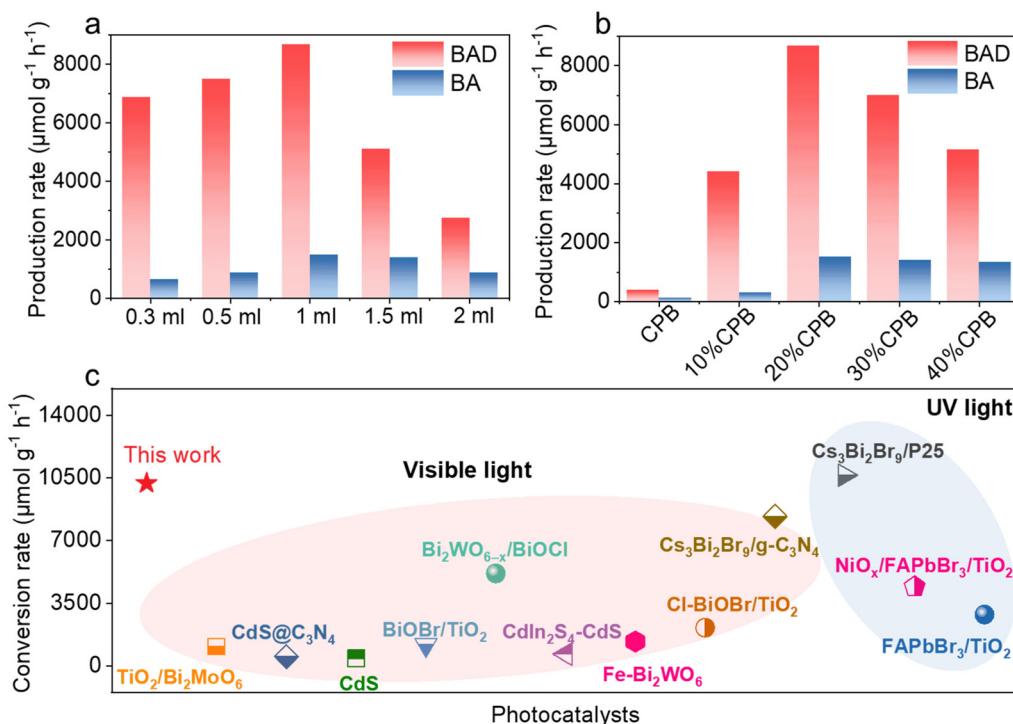


Fig. 5 (a) Photocatalytic oxidation of toluene with different toluene amounts in acetonitrile solvent over 20%CPB/TiO₂. The total volume is 3 ml. (b) Photocatalytic oxidation of toluene over blank TiO₂, CPB/TiO₂ composite and blank CsPbBr₃. (c) Performance comparison with reported photocatalysts for UV and visible-light-driven selective oxidation of toluene.

be due to the severe charge recombination caused by the large particle size of CsPbBr₃. For blank TiO₂, it presents no activity. This is reasonable since the TiO₂ has no visible light absorption and cannot be excited by visible light. In contrast, after the hybridization of CsPbBr₃ with TiO₂, the photocatalytic performances of all the hierarchical CPB/TiO₂ heterojunctions are significantly improved. The best photocatalytic toluene oxidation activity is achieved over the 20%CPB/TiO₂ composite, which shows a toluene conversion rate of 10 200 $\mu\text{mol g}^{-1} \text{h}^{-1}$ (with a BAD production rate of 8670 $\mu\text{mol g}^{-1} \text{h}^{-1}$ and a BA generation rate of 1530 $\mu\text{mol g}^{-1} \text{h}^{-1}$). The photoactivity is about 20 times higher than that of blank CsPbBr₃, which is also among the top photocatalytic performances reported so far for UV and visible-light-driven selective oxidation of toluene (Fig. 5c and Table S2†). The apparent quantum efficiency (AQE) of the 20%CsPbBr₃/TiO₂ composite reaches 2.9% at $\lambda = 420$ nm for the transformation of toluene into BA and BAD (Fig. S14†). The gas chromatography-mass spectrometry (GC-MS) analysis of the reaction solution after light irradiation reveals four peaks, which are ascribed to the acetonitrile solvent, toluene reactant, BAD and BA products (Fig. S8†). No other product or intermediate is detected, validating the high selectivity of the reaction. With the increase of CsPbBr₃ loading to higher contents (30% and 40%), it results in a performance degradation. This may be ascribed to the fact that: (1) an excess of halide perovskite tends to aggregate into large particles, which will lead to longer migration distances of charge carriers and increase charge recombination; (2) the

coverage of excessive and oversized CsPbBr₃ on the TiO₂ surface will lead to the reduction of the exposed surface area, inhibiting the adsorption of toluene molecules.

Furthermore, the broad applicability of the CPB/TiO₂ photocatalyst is investigated for the photocatalytic selective oxidation of C(sp³)-H of toluene derivatives with different substituents. As shown in Table 1, these aromatics are efficiently converted into the corresponding aldehydes and alcohols. The selectivity for the aldehyde product is higher than 70%. Notably, the substrate with electron-withdrawing substituents (–F, –Cl, and –Br) displays lower photocatalytic activity. This can be attributed to the fact that the electron-withdrawing groups on the benzene ring inhibit the abstraction of hydrogen from the methyl group.^{49,50} In addition, *p*-xylene shows a higher toluene conversion rate (12 746 $\mu\text{mol g}^{-1} \text{h}^{-1}$) than its isomers of *o*-xylene (9900 $\mu\text{mol g}^{-1} \text{h}^{-1}$) and *m*-xylene (10 930 $\mu\text{mol g}^{-1} \text{h}^{-1}$), which can be attributed to the steric hindrance of the methyl groups hindering the reactant adsorption and activation on the catalyst surface.^{51,52}

Moreover, the cycle test of the 20%CsPbBr₃/TiO₂ has been carried out. After repeating the photoactivity test for 4 cycles (Fig. S16†), the catalyst still maintains a high activity with negligible decrease in the conversion rate of toluene. In addition, the used 20%CsPbBr₃/TiO₂ has been further characterized by XRD and XPS (Fig. S17 and S18†). No obvious change in the crystal structure and surface chemical state is observed for the composite before and after the reaction. These results indicate the high stability of the CsPbBr₃/TiO₂ composite.

Table 1 Photocatalytic oxidation of $C(sp^3)$ -H in substituted toluene over 20%CPB/TiO₂^a

| Entry | Substrates | Conversion rate ($\mu\text{mol g}^{-1} \text{h}^{-1}$) | Selectivity (%) | |
|-------|------------|--|-----------------|----|
| | | | A | B |
| 1 | | 10 200 | 85 | 15 |
| 2 | | 5950 | 83 | 17 |
| 3 | | 9040 | 88 | 12 |
| 4 | | 9770 | 87 | 13 |
| 5 | | 9900 | 76 | 24 |
| 6 | | 10 930 | 72 | 28 |
| 7 | | 12 746 | 71 | 29 |

^a Reaction conditions: catalyst (10 mg 20%CPB/TiO₂), substrate (1 mL), MeCN (2 mL), 1 atm of O₂, 2 h irradiation with visible light ($\lambda > 420$ nm).

Photoelectric properties

In order to better understand the reasons for the improved photocatalytic performance, the band structures of the CsPbBr₃ and the TiO₂ are investigated using Mott–Schottky (M–S) measurements and the DRS analysis. As shown in Fig. 6a and b, the positive slopes indicate that CsPbBr₃ and TiO₂ are typical n-type semiconductors.⁵³ The flat band potentials (E_{FB}) are calculated to be -0.86 V and -0.34 V (vs. NHE) for CsPbBr₃ and TiO₂, respectively. Usually, the conduction band potential (E_{CB}) for an n-type semiconductor is more negative of about 0.1 eV than that of E_{FB} .⁵⁴ Thus, the E_{CB} values of CsPbBr₃ and TiO₂ are determined to be -0.96 V and -0.44 V (vs. NHE), respectively. In addition, the corresponding bandgaps of TiO₂ and CsPbBr₃ are estimated by Tauc plots transformed from the DRS spectra (Fig. S9†), which are 3.20 eV and 2.28 eV, respectively. Based on these, the valence band positions (E_{VB}) of CsPbBr₃ and TiO₂ are calculated to be 1.32 V and 2.76 V. As a result, a type-II heterojunction is formed between CsPbBr₃ and TiO₂ because of the staggered band structures.

To study the influence of the heterojunction structure on the transfer behavior of photogenerated charge carriers, transient photocurrent and electrochemical impedance spectra (EIS) tests are performed. As shown in Fig. 6c, under visible light irradiation, both CsPbBr₃ and CPB/TiO₂ show rapid and stable photocurrent responses, while TiO₂ does not. This can be

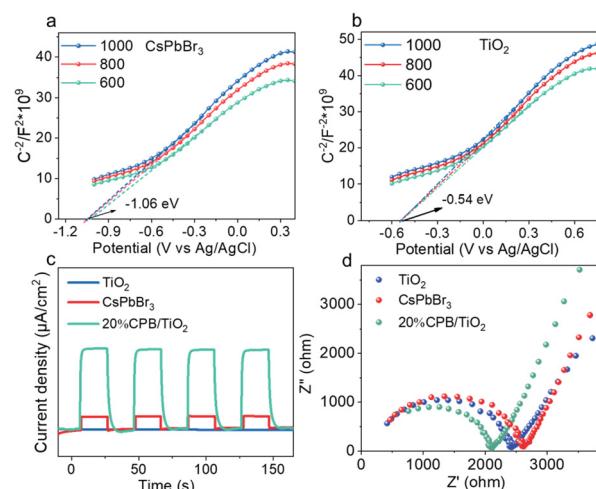


Fig. 6 (a and b) M–S plots of CsPbBr₃ and TiO₂. (c) Transient photocurrent responses, and (d) EIS Nyquist plots of blank TiO₂, CsPbBr₃ and the CPB/TiO₂ composite.

attributed to the inability of TiO₂ to be excited by visible light (Fig. 1d). The photocurrent intensity of blank CsPbBr₃ is markedly lower than that of 20% CPB/TiO₂. This should be due to the agglomerated large particle size of the blank CsPbBr₃, which leads to a severe recombination of photogenerated charge carriers.⁵⁴ Moreover, Fig. 6d shows the Nyquist plots of the samples, which is employed to investigate the interfacial charge transfer efficiency.⁵⁵ In general, the smaller diameter of the semicircular arc in the Nyquist plots reflects the lower electron transfer resistance. It can be found that the 20%CPB/TiO₂ sample has the minimum arc radius, which means the best electronic conductivity and charge separation ability.^{56,57} Furthermore, the steady-state photoluminescence (PL) spectra are also used to examine the charge separation efficiency. As shown in Fig. S19,† the 20%CsPbBr₃/TiO₂ composite shows a much lower PL intensity than that of CsPbBr₃, revealing that the charge recombination is significantly suppressed in the composite. In addition, the TiO₂ shows no obvious PL signal. This is in accordance with the photocurrent analysis that the TiO₂ is unable to be excited to generate charge carriers by visible light. These photoelectrochemical findings highlight that the construction of the type-II heterojunction between CsPbBr₃ and TiO₂ could effectively accelerate charge transfer, thus contributing to improving the photocatalytic performance.

Furthermore, for heterogeneous photocatalytic reactions, the effective adsorption of the reactant on the catalyst surface is another requisite for the ignition of the redox reaction.^{23,58–60} The BET surface area and porous structure analyses of the TiO₂, CsPbBr₃ and 20%CPB/TiO₂ samples have shown that the introduction of TiO₂ nanoflower significantly improves the specific surface area and pore volume of 20% CPB/TiO₂ in comparison with that of blank TiO₂ (Fig. S6 and Table S1†). Generally, a larger specific surface area and a porous structure enable better adsorption capacity, and

exposure of more active sites of catalysts. To further reveal the contribution of the heterostructure for the reactant adsorption, Fourier transform infrared (FTIR) spectroscopy is used to identify the adsorbed toluene species on the CsPbBr_3 , TiO_2 and 20%CPB/ TiO_2 surface. As shown in Fig. 7a, for all three samples after adsorption equilibrium, the typical absorption peaks of toluene are observed, including the C–H stretching vibration of the aromatic ring at 3083 and 3038 cm^{-1} , the skeleton vibration of the aromatic ring at 1606 and 1495 cm^{-1} , and the C–H symmetric and asymmetric stretching of the methylene group at 2934 and 2875 cm^{-1} .^{61,62} Notably, the signal of toluene molecules of 20%CPB/ TiO_2 is obviously higher than that of blank CsPbBr_3 , yet is lower than that of blank TiO_2 . The result indicates that the introduction of TiO_2 can promote the toluene adsorption capacity of CPB/ TiO_2 , which is conducive to the catalytic conversion.

Finally, to investigate the influence of the hierarchical flower-like nanostructure constructed using 2D nanoflake sub-units on the photocatalytic performance, a collapsed 20%CPB/ TiO_2 catalyst (marked as 20%CPB/ TiO_2 –C) without such structure has been fabricated for comparison. As shown in Fig. 7b, the photoactivity test reveals that the 20%CPB/ TiO_2 –C has a BAD generation rate of 6000 $\mu\text{mol g}^{-1} \text{h}^{-1}$ and a BA production rate of 1250 $\mu\text{mol g}^{-1} \text{h}^{-1}$, which is notably lower than the CPB/ TiO_2 catalyst. Fig. S10† shows the morphology analysis of the 20%CPB/ TiO_2 –C catalyst, which reveals a bulky grain structure with a rough surface. CsPbBr_3 nanoparticles are dispersed on the surface of the massive TiO_2 . The size of the CsPbBr_3 particles in the composite is also much smaller than that of blank CsPbBr_3 , which once again proves that TiO_2 plays a critical role in inhibiting the growth of CsPbBr_3 . Nevertheless, compared with 20%CPB/ TiO_2 , the size of the CsPbBr_3 particles is much larger in the 20%CPB/ TiO_2 –C catalyst. The result indicates that the TiO_2 nanoflakes are more beneficial for preventing the agglomeration of the CsPbBr_3 particles.

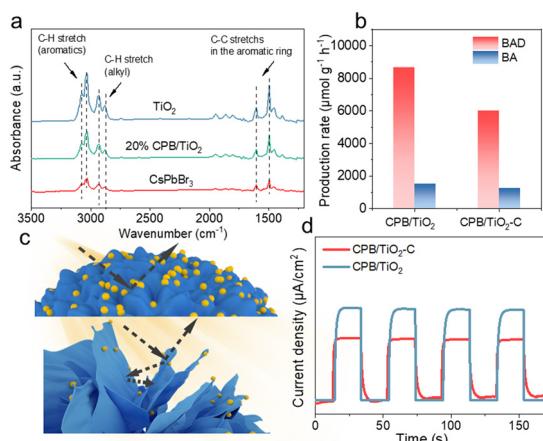


Fig. 7 (a) FTIR spectra of 20%CPB/ TiO_2 , TiO_2 and CsPbBr_3 after adsorption of saturated toluene. (b) Photoactivity comparison between CPB/ TiO_2 and CPB/ TiO_2 –C. (c) Schematic diagram of light absorption over CPB/ TiO_2 and CPB/ TiO_2 –C. (d) Transient photocurrent responses of CPB/ TiO_2 and CPB/ TiO_2 –C.

In addition, UV-vis DRS is performed to study the optical absorption property of the 20%CPB/ TiO_2 –C catalyst. The sample shows a similar absorption edge as that of 20%CPB/ TiO_2 , but the light absorption intensity in the range of 200–550 nm is lower (Fig. S11†). The result indicates that the 3D hierarchical CPB/ TiO_2 structure is more efficient for solar energy collection, which can be attributed to the multiple light reflection and refraction caused by the vertical nanoflakes, as schematically illustrated in Fig. 7c. Meanwhile, the transient photocurrent response test shows that the 20%CPB/ TiO_2 catalyst exhibits a higher photocurrent density than that of CPB/ TiO_2 –C under visible light irradiation, indicating more efficient charge transfer (Fig. 7d). This can be related to the fact that TiO_2 nanoflakes facilitate the formation of smaller CsPbBr_3 particle, which could shorten the charge transfer distance to the surface and promote the interfacial charge separation. Hence, to sum up, the construction of the unique hierarchical CPB/ TiO_2 structure greatly enhances the photocatalytic performance due to the existence of TiO_2 nanoflakes, which (1) greatly prohibits the aggregation of CsPbBr_3 , forming much smaller perovskite particles that shorten the charge transfer distance; (2) increases light absorption by multiple reflection and scattering between the nanoflakes structure that benefits the solar energy harvesting and conversion; (3) enhances the adsorption of toluene molecules and promotes the surface reaction rates.

Photocatalytic mechanism

To elucidate the photocatalytic mechanism of toluene oxidation over the CPB/ TiO_2 photocatalyst, a series of control experiments have been conducted in the absence of O_2 or with the addition of specific radical scavengers. As shown in Fig. 8a, toluene oxidation is almost completely suppressed when O_2 is replaced by Ar, indicating that O_2 is indispensable. When isopropanol (IPA) is added into the reaction system as a scavenger of hydroxyl radicals ($\cdot\text{OH}$), it has almost no effect on toluene conversion, suggesting that $\cdot\text{OH}$ is rarely involved in the reaction. In contrast, whether adding ammonium oxalate (AO) to eliminate holes (h^+) or butylated hydroxytoluene (BHT) to capture carbon-centered radicals, the reaction rate significantly reduces. Besides, the toluene conversion is also significantly decreased when BQ is added as a superoxide free radical (O_2^-) scavenger. The above results clearly indicate that O_2^- , h^+ , and carbon-centered radicals play key roles in the photocatalytic selective oxidation of toluene.

Subsequently, to further identify the existence of O_2^- , electron paramagnetic resonance (EPR) spectroscopy was employed using 5,5-dimethyl-pyrroline-N-oxide (DMPO) as a trapping agent. As shown in Fig. S12† and Fig. 8b, no DMPO- O_2^- signal is detected under dark conditions. After visible light irradiation, distinct signals of DMPO- O_2^- are observed for both CsPbBr_3 and CPB/ TiO_2 , while no signals are detected from TiO_2 . The CPB/ TiO_2 catalyst exhibits a higher ability to generate more O_2^- radicals than that of pure CsPbBr_3 , which is important to promote the oxidation of toluene. Moreover, no DMPO- $\cdot\text{OH}$ signal is observed under the

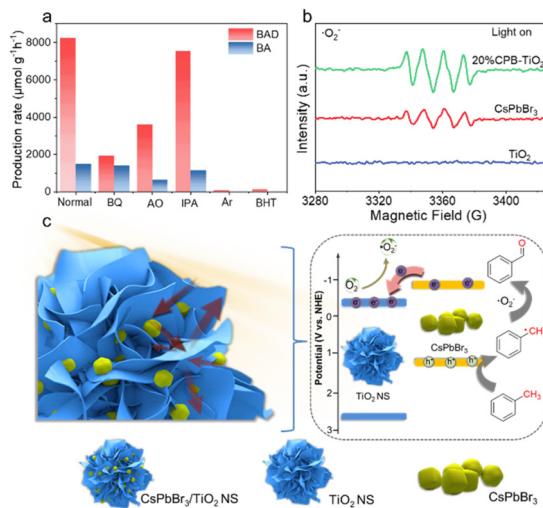


Fig. 8 (a) Photocatalytic toluene oxidation in the absence or presence of various radical scavengers. (b) EPR spectra of DMPO-·O₂[·]. (c) Schematic illustration of the proposed mechanism of photocatalytic oxidation of toluene over the CPB/TiO₂ composite.

same conditions, demonstrating that ·OH is absent in the reaction process (Fig. S13 and S15†).

Based on the above analyses, a possible photocatalytic reaction mechanism over the hierarchical CPB/TiO₂ heterojunction is proposed. As schematically illustrated in Fig. 8c, upon photoexcitation, electrons and holes are generated in the conduction band (CB) and the valence band (VB) of CsPbBr₃. Due to the staggered energy bands, the photogenerated electrons in the CB of CsPbBr₃ can efficiently migrate towards the CB of TiO₂ and leave holes on the VB of CsPbBr₃, which prolongs the lifetime of the photogenerated charge carriers. After that, molecular O₂ can be activated by electrons on the CB of TiO₂. Meanwhile, photogenerated holes oxidize the toluene to produce benzyl radicals (·CH₂-R) on the VB of CsPbBr₃. Then, the ·O₂[·] radical reacts with the benzyl radicals to produce benzaldehyde.

Conclusions

In summary, we have designed and synthesized a hierarchical CPB/TiO₂ heterojunction as an advanced photocatalyst for efficient visible-light-driven toluene oxidation by assembling CsPbBr₃ nanoparticles onto nanoflower-shaped TiO₂ with 2D nanoflake subunits. The formed CPB/TiO₂ composite integrates the structural and electronical merits of the nanoflower-shaped TiO₂ and halide perovskite CsPbBr₃, which not only enhances solar light utilization, but also enhances the adsorption of the toluene reactant, and boosts the separation and transportation of photogenerated carriers. A high toluene oxidation rate of 10 200 μmol g⁻¹ h⁻¹ is achieved over the optimal CPB/TiO₂ composite, which is about 20-fold higher than that of blank CsPbBr₃. The study demonstrates the significance of rational design of well-defined hierarchical heterojunction cat-

alysts over metal halide perovskites for efficient photocatalytic redox reactions.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the National Key Research and Development Program of China (2019YFC1908203), the National Natural Science Foundation of China (22178057 and 21905049), the Natural Science Foundation of Fujian Province (2020J01201 and 2021J01197), the Research Foundation of the Academy of Carbon Neutrality of Fujian Normal University (TZH2022-07), and the Award Program for Minjiang Scholar Professorship.

References

- W. Wu, G. Zhang, J. Zhang, G. Wang, C.-H. Tung and Y. Wang, *Chem. Eng. J.*, 2021, **404**, 126433.
- X. Li, T. Wang, X. Tao, G. Qiu, C. Li and B. Li, *J. Mater. Chem. A*, 2020, **8**, 17657–17669.
- S. Okunaka, H. Tokudome and Y. Hitomi, *J. Catal.*, 2020, **391**, 480–484.
- S. Zhang, W. Huang, X. Fu, X. Zheng, S. Meng, X. Ye and S. Chen, *Appl. Catal., B*, 2018, **233**, 1–10.
- J. Li, B. Ren, X. Yan, P. Li, S. Gao and R. Cao, *J. Catal.*, 2021, **395**, 227–235.
- C. Xu, F. Yang, B. Deng, Y. Zhuang, D. Li, B. Liu, W. Yang and Y. Li, *J. Catal.*, 2020, **383**, 1–12.
- J. Li, S. Zhang, S. Gui, G. Chen, Y. Wang, Z. Wang, X. Zheng, S. Meng, C. Ruan and S. Chen, *Appl. Surf. Sci.*, 2023, **611**, 155616.
- Q. Zhang, J. Wang, X. Ye, Z. Hui, L. Ye, X. Wang and S. Chen, *ACS Appl. Mater. Interfaces*, 2019, **11**, 46735–46745.
- Y. Liu, L. Chen, Q. Yuan, J. He, C. T. Au and S. F. Yin, *Chem. Commun.*, 2016, **52**, 1274–1277.
- M. Zhou, S. Li, S. Wang, Z. Jiang, C. Yang, F. Guo, X. Wang and W.-K. Ho, *Appl. Surf. Sci.*, 2022, **599**, 153985.
- M. Zhang, W. Sun, H. Lv and Z.-H. Zhang, *Curr. Opin. Green Sustainable Chem.*, 2021, **27**, 100390.
- Z. Zhang, Y. Liang, H. Huang, X. Liu, Q. Li, L. Chen and D. Xu, *Angew. Chem., Int. Ed.*, 2019, **58**, 7263–7267.
- M. Zhang, Z. Li, X. Xin, J. Zhang, Y. Feng and H. Lv, *ACS Catal.*, 2020, **10**, 14793–14800.
- T. Chen, B. Weng, S. Lu, H. Zhu, Z. Chen, L. Shen, M. B. J. Roeffaers and M. Q. Yang, *J. Phys. Chem. Lett.*, 2022, **13**, 6559–6565.
- R. Cheng, J. A. Steele, M. B. J. Roeffaers, J. Hofkens and E. Debroye, *ACS Appl. Energy Mater.*, 2021, **4**, 3460–3468.

16 H. Huang, J. Zhao, Y. Du, C. Zhou, M. Zhang, Z. Wang, Y. Weng, J. Long, J. Hofkens, J. A. Steele and M. B. J. Roeffaers, *ACS Nano*, 2020, **14**, 16689–16697.

17 H. Huang, H. Yuan, J. Zhao, G. Solís-Fernández, C. Zhou, J. W. Seo, J. Hendrix, E. Debroye, J. A. Steele, J. Hofkens, J. Long and M. B. J. Roeffaers, *ACS Energy Lett.*, 2018, **4**, 203–208.

18 H. Huang, H. Yuan, K. P. F. Janssen, G. Solís-Fernández, Y. Wang, C. Y. X. Tan, D. Jonckheere, E. Debroye, J. Long, J. Hendrix, J. Hofkens, J. A. Steele and M. B. J. Roeffaers, *ACS Energy Lett.*, 2018, **3**, 755–759.

19 C. Chen, J. Zhou, J. Geng, R. Bao, Z. Wang, J. Xia and H. Li, *Appl. Surf. Sci.*, 2020, **503**, 144287.

20 Y. Dai, C. Poidevin, C. Ochoa-Hernandez, A. A. Auer and H. Tuysuz, *Angew. Chem., Int. Ed.*, 2020, **59**, 5788–5796.

21 F. Xu, K. Meng, B. Cheng, S. Wang, J. Xu and J. Yu, *Nat. Commun.*, 2020, **11**, 4613.

22 M.-Q. Yang, J. Dan, S. J. Pennycook, X. Lu, H. Zhu, Q.-H. Xu, H. J. Fan and G. W. Ho, *Mater. Horiz.*, 2017, **4**, 885–894.

23 X. Lin, Z. Xie, B. Su, M. Zheng, W. Dai, Y. Hou, Z. Ding, W. Lin, Y. Fang and S. Wang, *Nanoscale*, 2021, **13**, 18070–18076.

24 S. Wang, B. Y. Guan and X. W. Lou, *Energy Environ. Sci.*, 2018, **11**, 306–310.

25 L. Zhu, M. Hong and G. W. Ho, *Nano Energy*, 2015, **11**, 28–37.

26 L. He, W. Zhang, K. Zhao, S. Liu and Y. Zhao, *J. Mater. Chem. A*, 2022, **10**, 4758–4769.

27 Q. Shen, S. Zhou, F.-L. Yang, X. Wang and X. Han, *J. Mater. Chem. A*, 2022, **10**, 4974–4980.

28 S. Wang, B. Y. Guan, X. Wang and X. W. D. Lou, *J. Am. Chem. Soc.*, 2018, **140**, 15145–15148.

29 S. Wang, B. Y. Guan and X. W. D. Lou, *J. Am. Chem. Soc.*, 2018, **140**, 5037–5040.

30 T. Zhu, L. Zhu, J. Wang and G. W. Ho, *J. Mater. Chem. A*, 2016, **4**, 13916–13922.

31 Z. Chen, F. Guo, H. Sun, Y. Shi and W. Shi, *J. Colloid Interface Sci.*, 2022, **607**, 1391–1401.

32 K. Lan, Y. Liu, W. Zhang, Y. Liu, A. Elzatahry, R. Wang, Y. Xia, D. Al-Dhayan, N. Zheng and D. Zhao, *J. Am. Chem. Soc.*, 2018, **140**, 4135–4143.

33 Q. Sun, W. Ye, J. Wei, L. Li, J. Wang, J.-H. He and J.-M. Lu, *J. Alloys Compd.*, 2022, **893**, 162326.

34 J. Hafner, *J. Comput. Chem.*, 2008, **29**, 2044–2078.

35 G. Kresse and J. Hafner, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **48**, 13115–13118.

36 L. Rao, Y. Tang, C. Yan, J. Li, G. Zhong, K. Tang, B. Yu, Z. Li and J. Z. Zhang, *J. Mater. Chem. C*, 2018, **6**, 5375–5383.

37 J. Liu, L. Zhu, S. Xiang, Y. Wei, M. Xie, H. Liu, W. Li and H. Chen, *Sustainable Energy Fuels*, 2019, **3**, 184–194.

38 G. Gao, Q. Xi, H. Zhou, Y. Zhao, C. Wu, L. Wang, P. Guo and J. Xu, *Nanoscale*, 2017, **9**, 12032–12038.

39 L. Zhang, Q. Zeng and K. Wang, *J. Phys. Chem. Lett.*, 2017, **8**, 3752–3758.

40 X. Mo, X. Li, G. Dai, P. He, J. Sun, H. Huang and J. Yang, *Nanoscale*, 2019, **11**, 21386–21393.

41 D. M. Calistrut, L. Mihut, S. Lefrant and I. Baltog, *J. Appl. Phys.*, 1997, **82**, 5391–5395.

42 H. J. Kong, D. H. Won, J. Kim and S. I. Woo, *Chem. Mater.*, 2016, **28**, 1318–1324.

43 I.-S. Cho, D. W. Kim, S. Lee, C. H. Kwak, S.-T. Bae, J. H. Noh, S. H. Yoon, H. S. Jung, D.-W. Kim and K. S. Hong, *Adv. Funct. Mater.*, 2008, **18**, 2154–2162.

44 S. K. Lakhera, H. Y. Hafeez, R. Venkataramana, P. Veluswamy, H. Choi and B. Neppolian, *Appl. Surf. Sci.*, 2019, **487**, 1289–1300.

45 J. Yu and A. Kudo, *Adv. Funct. Mater.*, 2006, **16**, 2163–2169.

46 C. Q. Li, X. Du, S. Jiang, Y. Liu, Z. L. Niu, Z. Y. Liu, S. S. Yi and X. Z. Yue, *Adv. Sci.*, 2022, **9**, e2201773.

47 J. Kou, C. Lu, J. Wang, Y. Chen, Z. Xu and R. S. Varma, *Chem. Rev.*, 2017, **117**, 1445–1514.

48 J. Wu, Y. Wang, S. Zhang, Y. Liu and F. Wang, *Appl. Catal., B*, 2023, **332**, 122741.

49 H. Han, X. Zheng, C. Qiao, Z. Xia, Q. Yang, L. Di, Y. Xing, G. Xie, C. Zhou, W. Wang and S. Chen, *ACS Catal.*, 2022, **12**, 10668–10679.

50 R. Yuan, S. Fan, H. Zhou, Z. Ding, S. Lin, Z. Li, Z. Zhang, C. Xu, L. Wu, X. Wang and X. Fu, *Angew. Chem., Int. Ed.*, 2013, **52**, 1035–1039.

51 W. Sheng, X. Wang, Y. Wang, S. Chen and X. Lang, *ACS Catal.*, 2022, **12**, 11078–11088.

52 X. Li, S. Lyu and X. Lang, *Environ. Res.*, 2021, **195**, 110851.

53 Z. Dong, Z. Zhang, Y. Jiang, Y. Chu and J. Xu, *Chem. Eng. J.*, 2022, **433**, 133762.

54 X. Li, S. Lu, J. Yi, L. Shen, Z. Chen, H. Xue, Q. Qian and M. Q. Yang, *ACS Appl. Mater. Interfaces*, 2022, **14**, 25297–25307.

55 W. Liao, W. Chen, S. Lu, S. Zhu, Y. Xia, L. Qi, M. Q. Yang and S. Liang, *ACS Appl. Mater. Interfaces*, 2021, **13**, 38239–38247.

56 T. Shan, L. Luo, T. Chen, L. Deng, M. Li, X. Yang, L. Shen and M.-Q. Yang, *Green Chem.*, 2023, **25**, 2745–2756.

57 M. Q. Yang, C. F. Tan, W. Lu, K. Zeng and G. W. Ho, *Adv. Funct. Mater.*, 2020, **30**, 2004460.

58 J. Wang, Z. Wang, J. Zhang, S. P. Chai, K. Dai and J. Low, *Nanoscale*, 2022, **14**, 18087–18093.

59 L. Liu, Z. Wang, J. Zhang, O. Ruzimuradov, K. Dai and J. Low, *Adv. Mater.*, 2023, **35**, e2300643.

60 S. Lu, B. Weng, A. Chen, X. Li, H. Huang, X. Sun, W. Feng, Y. Lei, Q. Qian and M.-Q. Yang, *ACS Appl. Mater. Interfaces*, 2021, **13**, 13044–13054.

61 J. Wang, J. Li, W. Yang, Y. Liu, H. Wang, Q. Geng and F. Dong, *Appl. Catal., B*, 2021, **297**, 120489.

62 X. Zhao, B. Deng, F. Li, M. Huang, Y. Sun, J. Li and F. Dong, *J. Hazard. Mater.*, 2021, **420**, 126577.