


Cite this: *RSC Adv.*, 2023, 13, 18974

# Dual functional WO<sub>3</sub>/BiVO<sub>4</sub> heterostructures for efficient photoelectrochemical water splitting and glycerol degradation

Piangjai Peerakiatkhajohn,<sup>a</sup> Jung-Ho Yun,<sup>b</sup> Teera Butburee,<sup>c</sup> Miaoqiang Lyu,<sup>d</sup> Chawalit Takoon<sup>e</sup> and Supphasin Thaweesak<sup>\*f</sup>

Dual functional heterojunctions of tungsten oxide and bismuth vanadate (WO<sub>3</sub>/BiVO<sub>4</sub>) photoanodes are developed and their applications in photoelectrochemical (PEC) water splitting and mineralization of glycerol are demonstrated. The thin-film WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrode was fabricated by a facile hydrothermal method. The morphology, chemical composition, crystalline structure, chemical state, and optical absorption properties of the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes were characterized systematically. The WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrode exhibits a good distribution of elements and a well-crystalline monoclinic WO<sub>3</sub> and monoclinic scheelite BiVO<sub>4</sub>. The light-absorption spectrum of the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes reveals a broad absorption band in the visible light region with a maximum absorption of around 520 nm. The dual functional WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes achieved a high photocurrent density of 6.85 mA cm<sup>-2</sup>, which is 2.8 times higher than that of the pristine WO<sub>3</sub> photoelectrode in the presence of a mixture of 0.5 M Na<sub>2</sub>SO<sub>4</sub> and 0.5 M glycerol electrolyte under AM 1.5 G (100 mW cm<sup>-2</sup>) illumination. The superior PEC performance of the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrode was attributed to the synergistic effects of the superior crystal structure, light absorption, and efficient charge separation. Simultaneously, glycerol plays an essential role in increasing the efficiency of hydrogen production by suppressing charge recombination in the water redox reaction. Moreover, the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrode shows the total organic carbon (TOC) removal efficiency of glycerol at about 82% at 120 min. Notably, the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrode can be a promising photoelectrode for simultaneous hydrogen production and mineralization of glycerol with a simple, economical, and environmentally friendly approach.

Received 23rd April 2023  
Accepted 15th June 2023

DOI: 10.1039/d3ra02691d

rsc.li/rsc-advances

## Introduction

Clean water and clean energy are two urgent global goals to achieve a better and more sustainable future for human society. Biodiesel is a renewable energy that holds various aspects of sustainability.<sup>1</sup> However, during biodiesel production glycerol by-product is generated in large amounts. Crude glycerol is

generated between 60 and 70 wt% from the transesterification process.<sup>2</sup>

Although, glycerol is used widely in various industries such as pharmaceutical, medicine, cosmetics, toiletries, food, and personal care products, the glycerol by-product from biofuel production is still in surplus. Therefore, the surplus crude glycerol has resulted in its price reduction by 60% and has been regarded as a waste stream that required proper disposal.<sup>3,4</sup> In addition, continuously increasing energy demand and fossil energy exhaustion have driven the energy price to rise rapidly. Furthermore, the combustion of fossil fuels releases carbon dioxide (CO<sub>2</sub>), which is one of the greenhouse gases that primarily causes global warming. To overcome these issues, the next-generation energy source should be sustainable and clean. Hydrogen gas has been considered a high-efficiency, storable, transportable, renewable, and environmentally-friendly energy.<sup>5</sup>

Several engineering strategies have been studies to sustainably produce H<sub>2</sub> for instance pyrolysis,<sup>6</sup> thermolysis,<sup>7</sup> electrolysis,<sup>8–10</sup> biophotolysis,<sup>11</sup> and photoelectrolysis.<sup>12</sup>

Photoelectrolysis is a process of water splitting by the integration of solar energy and electric power also known as the

<sup>a</sup>Faculty of Environment and Resource Studies, Mahidol University, Nakhon Pathom 73170, Thailand. E-mail: piangjai.pee@mahidol.ac.th

<sup>b</sup>Department of Environmental Science and Engineering, College of Engineering, Kyung Hee University, 1732 Deogyong-daero, Giheung-gu, Yongin-si, Gyeonggi-do, 17104, Republic of Korea. E-mail: junggho.yun@khu.ac.kr

<sup>c</sup>National Nanotechnology Center, National Science and Technology Development Agency, 111 Thailand Science Park, Pathum Thani 12120, Thailand. E-mail: teera.but@nanotec.or.th

<sup>d</sup>Nanomaterials Centre, School of Chemical Engineering and Australian Institute for Bioengineering and Nanotechnology (AIBN), The University of Queensland, St Lucia, QLD 4123, Australia. E-mail: m.lyu@uq.edu.au

<sup>e</sup>Mahidol University Frontier Research Facility (MU-FRF), Mahidol University, Nakhon Pathom 73170, Thailand. E-mail: chawalit.tak@mahidol.ac.th

<sup>f</sup>Department of Chemical Engineering, Faculty of Engineering, Burapha University, Chon Buri 20131, Thailand. E-mail: supphasin@eng.buu.ac.th



photoelectrochemical (PEC) process. The PEC process provides a sustainable way to produce  $H_2$  due to the most abundant of solar energy. The PEC water splitting has been extensively studied with the aim to improve the efficiency and stability.<sup>13,14</sup> PEC water splitting from a semiconducting  $TiO_2$  photoanode under UV illumination was first reported by Fujishima and Honda in 1972.<sup>15</sup> Semiconductor electrodes play an important role in PEC water splitting. The primary reasons are PEC water splitting process requires three fundamental steps, including light absorption, photoexcited charge separation and transportation, and photoexcited charge reaction.<sup>13</sup> During the past five decades, earth-abundant and low-cost materials metal oxide semiconductors such as  $TiO_2$ ,<sup>16–18</sup>  $ZnO$ ,<sup>19</sup>  $WO_3$ ,<sup>20–22</sup>  $Fe_2O_3$ ,<sup>23,24</sup>  $Cu_2O$ ,<sup>25</sup> and  $BiVO_4$ <sup>26,27</sup> have been extensively explored as photocatalyst materials in the PEC system. These studies reveal that metal oxide materials have great potential to be promising photoelectrode materials for PEC water splitting. However, using a single semiconductor photocatalyst still holds great challenges for obtaining high PEC performance. For instance, insufficient light absorption,<sup>28</sup> inefficient charge separation and charge transportation,<sup>29</sup> and photo-corrosion are the main factors that limit the PEC water splitting performance.<sup>13,14,30</sup> Fortunately,  $WO_3$  and  $BiVO_4$  are two of the most promising photoanode materials, due to their chemically stable, and narrow band gap ( $WO_3$   $E_g = 2.5–2.7$  eV,  $BiVO_4$   $E_g = 2.4$  eV)<sup>20,26</sup> Especially, heterostructure  $WO_3/BiVO_4$  has been reported to improve charge transfer and alleviate charge recombination.<sup>29,31–33</sup>

Herein, we developed dual-function  $WO_3/BiVO_4$  photoelectrodes for both converting energy from renewable energy sources and simultaneously removal of glycerol pollutant. The  $WO_3/BiVO_4$  photoelectrode is composed of a superior structure of the monoclinic structure of  $WO_3$  and monoclinic scheelite structure of  $BiVO_4$  that provided good electron transport and photocatalytic activity, respectively.

In addition, the constructed type-II heterostructure of  $WO_3/BiVO_4$  effectively reduced charge recombination by facilitating electron separation between  $WO_3$  and  $BiVO_4$ . Furthermore, the oxygen vacancy in the  $WO_3/BiVO_4$  further improves the charge separation of  $WO_3/BiVO_4$ . The photoelectrochemical performance showed that the photocurrent density of the  $WO_3/BiVO_4$  photoelectrode was  $5.12\text{ mA cm}^{-2}$  at  $1.23\text{ V vs. RHE}$  under simulated AM 1.5G illumination, which was 2 times higher than that of the pristine  $WO_3$  photoelectrode in the presence of  $0.5\text{ M Na}_2\text{SO}_4$  electrolyte. The photocurrent density of the  $WO_3/BiVO_4$  photoelectrode was further improved to  $6.85\text{ mA cm}^{-2}$  and the TOC reached 80% in the presence of a mixture of  $0.5\text{ M Na}_2\text{SO}_4$  and  $0.5\text{ M glycerol}$  electrolyte. These results highlighted a simple and economical approach to fabricating  $WO_3/BiVO_4$  photoelectrodes that exhibit a considerable performance for dual PEC water splitting and contaminant degradation.

## Results and discussion

### Characterization of $WO_3$ and $WO_3/BiVO_4$ photoelectrodes

The morphology of the nanostructured photoelectrodes was examined by SEM as shown in Fig. 1(a–d). Fig. 1(a) shows that

the FTO substrate is densely and uniformly covered by vertically-aligned two-dimensional (2D)  $WO_3$  nanoplates. Fig. 1(b) is the higher magnification SEM image showing  $WO_3$  2D nanoplates with smooth surface and the thickness estimated to be  $\sim 100\text{ nm}$ . Fig. 1(c) and (d) show the  $WO_3$  nanoparticles which are deposited by  $BiVO_4$ , which is so called  $WO_3/BiVO_4$  thereafter. Obviously,  $WO_3/BiVO_4$  exhibits aligned structure, rougher surface, and much thicker than that of the bare  $WO_3$ , indicating successful deposition of  $BiVO_4$ .

Fig. 2(a) shows X-ray diffraction (XRD) patterns of  $WO_3$  and  $WO_3/BiVO_4$  photoelectrodes. The XRD patterns of  $WO_3$  were observed at  $23.1^\circ$ ,  $23.6^\circ$ ,  $24.3^\circ$ ,  $28.9^\circ$ ,  $34.1^\circ$ ,  $41.9^\circ$ ,  $48.2^\circ$ , and  $55.4^\circ$ , corresponding to the (002), (020), (200), (112), (202), (222), (040), and (402) planes, respectively. The diffraction peaks can be well indexed to the monoclinic crystal phase of  $WO_3$  (JCPDS No. 43-1035).<sup>32</sup> After depositing  $BiVO_4$  on  $WO_3$ , the XRD patterns of the  $WO_3/BiVO_4$  shows diffraction peaks at  $18.6^\circ$ ,  $28.8^\circ$ ,  $34.5^\circ$ , and  $46.7^\circ$ , corresponding to the (110), (121), (200), (240) planes of the monoclinic scheelite structure of  $BiVO_4$  (JCPDS No. 14-0688), respectively.<sup>34</sup> In addition, no obvious diffraction peaks of  $WO_3$  in the heterostructure  $WO_3/BiVO_4$ , and no other peaks are observed, suggesting that relatively thick layer of  $BiVO_4$  deposited on the  $WO_3$  surface. In addition, both monoclinic structure of  $WO_3$  and monoclinic scheelite structure of  $BiVO_4$  have been reported to have superior properties, where the monoclinic of  $WO_3$  phase was reported to have faster electron transport than orthorhombic phase.<sup>35</sup> Moreover, the monoclinic scheelite structure of  $BiVO_4$  was reported as the most photocatalytic active phase among the other two crystal structures, tetragonal scheelite structure, and tetragonal zircon structure.<sup>36</sup> The  $WO_3$  and  $WO_3/BiVO_4$  photoelectrodes were analyzed by FTIR to investigate the presence of functional groups, as shown in Fig. 2(b). The peaks at  $3500$  and  $1635\text{ cm}^{-1}$  can be ascribed to the stretching vibration and the bending mode of the hydroxyl group ( $-OH$ ), respectively. The hydroxyl group found was due to the atmospheric humidity adsorbed onto the surface.<sup>31</sup> In addition, the hydroxyl group provides a beneficial effect for trapping charge carriers to create reactive hydroxyl radical ( $OH^\cdot$ ) that effectively oxidizes organic molecules.<sup>37</sup> The crystal structure of  $WO_3$  and  $WO_3/BiVO_4$  was further investigated by Raman spectroscopy. Fig. 2(c) the Raman spectrum of  $WO_3$  showing three distinctive peaks at  $264$ ,  $705$ , and  $798\text{ cm}^{-1}$ , which can be ascribed to the O–W–O bending vibration and the W–O–W stretching vibration.<sup>31,38</sup> After  $BiVO_4$  was deposited on  $WO_3$ , the Raman spectrum of  $WO_3/BiVO_4$  reveals new peaks at  $324$  and  $360\text{ cm}^{-1}$ , indicating the asymmetric and symmetric deformation modes of the  $VO_4^{3-}$ , respectively.<sup>31</sup> These results indicate that  $WO_3/BiVO_4$  is successfully fabricated. In addition, it is obvious that the most intense peak of the  $WO_3$  and  $WO_3/BiVO_4$  shifts from  $798$  to  $813\text{ cm}^{-1}$ , suggesting non-stoichiometric of  $WO_3/BiVO_4$  due to oxygen vacancies.

To confirm the presence of oxygen vacancies, the chemical state of the  $WO_3/BiVO_4$  photoelectrodes was analyzed by XPS. Fig. 3(a–d) show high resolution spectra for the W 4f, O 1s, Bi 4f, and V 2p, respectively. As shown in Fig. 3(a), the W 4f spectra reveals four curves after convolution using Gaussian

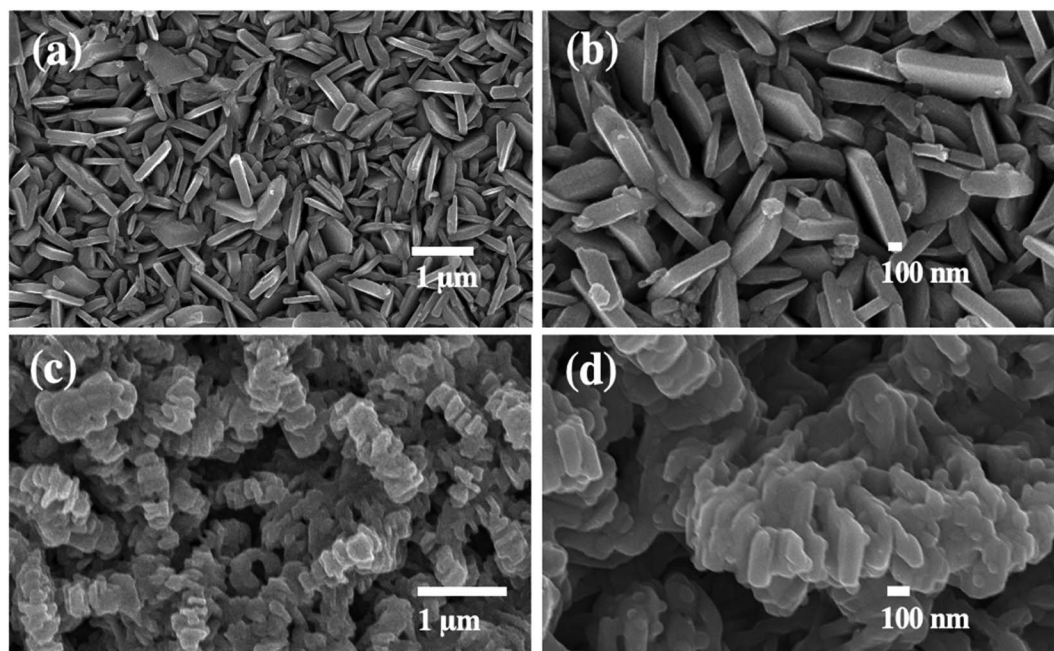


Fig. 1 SEM images of (a and b)  $\text{WO}_3$  and (c and d)  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.

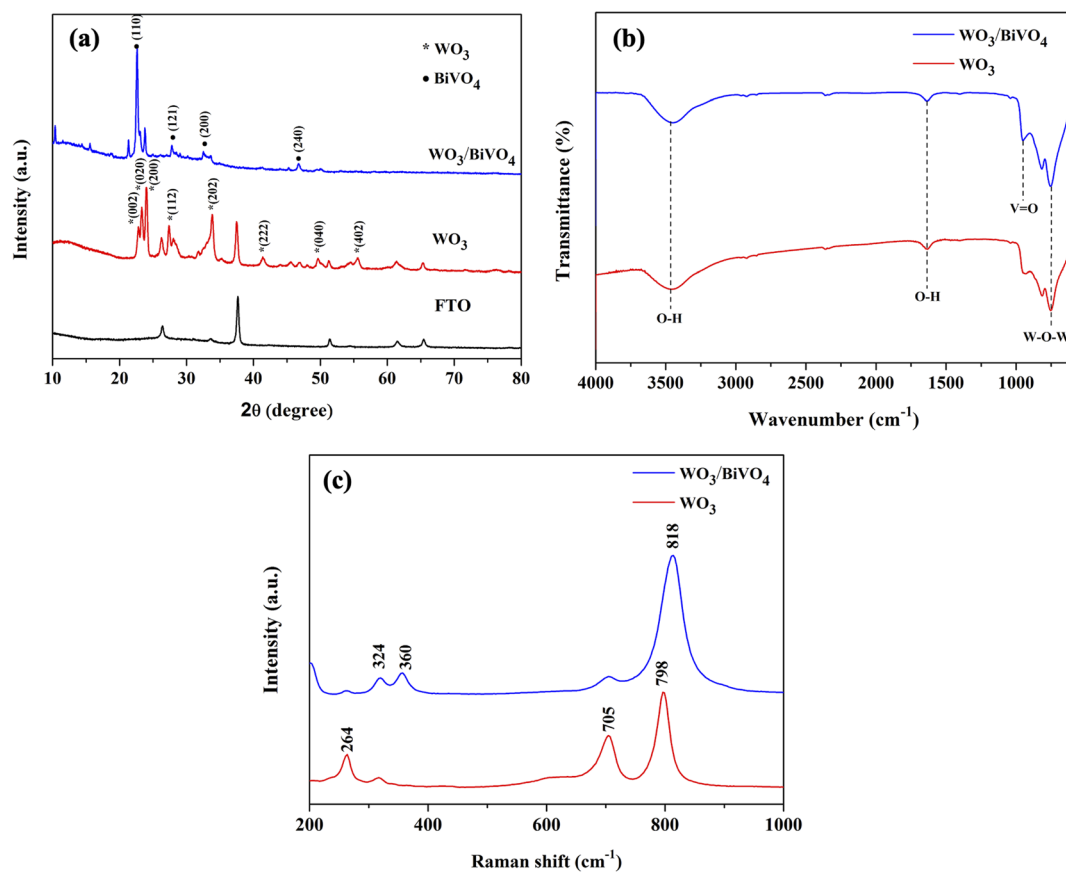


Fig. 2 (a) XRD patterns (b) FTIR spectra and (c) Raman spectra of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.



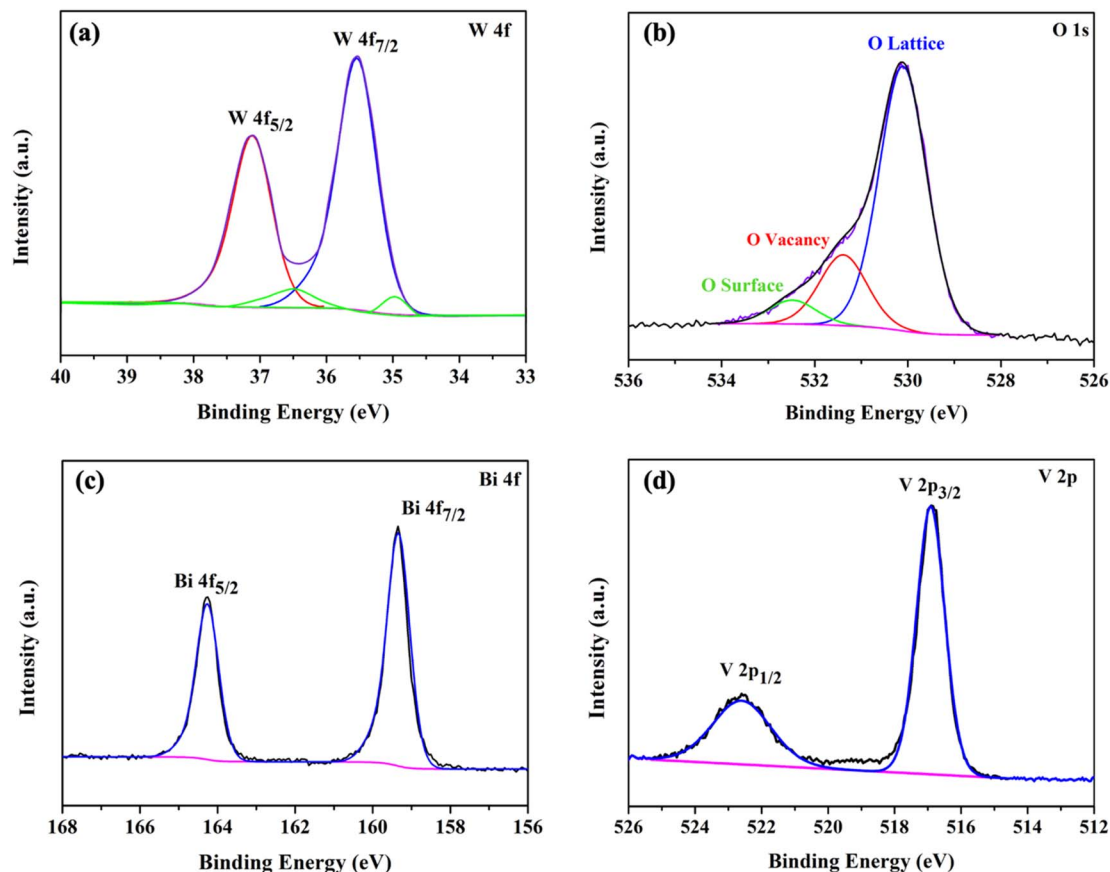


Fig. 3 XPS spectra of (a) W 4f (b) O 1s (c) Bi 4f and (d) V 2p of  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.

distribution. The two intense peaks at 35.3 and 37.4 eV can be ascribed to W 4f<sub>7/2</sub> and W 4f<sub>5/2</sub> of W<sup>6+</sup> state. The two low-intensity peaks at 34.6 and 36.7 eV corresponding to W 4f<sub>7/2</sub> and W 4f<sub>5/2</sub> of W<sup>5+</sup> state, indicating the presence of oxygen vacancies defects.<sup>39</sup> Fig. 3(b) shows O 1s spectra with a broad shoulder to the higher binding energy side, indicating the existence of several oxygen species. The intense peak at 530.1 eV corresponds to the lattice oxygen in metal oxides (O Lattice), while the other two oxygen peaks at 531.4 and 532.5 eV can be assigned to the surface defects (O vacancy), and the surface absorbed oxygen (O surface), respectively.<sup>31,40</sup> Fig. 3(c) reveals two typical peaks at 159.4 and 164.3 eV corresponding to Bi 4f<sub>7/2</sub> and Bi 4f<sub>5/2</sub> of Bi<sup>3+</sup> state.<sup>38</sup> Furthermore, Fig. 3(d) shows V 2p spectra with two peak located at 516.9 and 522.7 eV, which can be assigned to V 2p<sub>3/2</sub> and V 2p<sub>1/2</sub> of V<sup>5+</sup> state, respectively.<sup>31</sup>

The light absorption spectra of the photoelectrodes were analyzed using the UV-Vis DRS technique to reveal the light-harvesting property as shown in Fig. 4(a). The absorption edge of the  $\text{WO}_3$  nanoplates is around 470 nm, while the absorption range was extended to around 520 nm for  $\text{WO}_3/\text{BiVO}_4$ . The band gap of the  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  are 2.64 and 2.38 eV, respectively as shown in Fig. 4(b). The  $\text{WO}_3/\text{BiVO}_4$  samples showed good absorption in the visible light region, which can facilitate the enhancement of PEC properties under visible light irradiation.<sup>33,41</sup> Fig. 5(a) and (b) show TEM images and the

corresponding EDS elemental mapping of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes. As shown in Fig. 5(a), W and O elements are uniformly distributed on the nanoplates without other impurities.

The weight percentage of W and O elements were estimated at 80.7 wt% and 19.3 wt%, respectively. Fig. 5(b) shows the elemental mapping of  $\text{WO}_3/\text{BiVO}_4$  photoelectrode. The result shows that W and O are uniformly distributed throughout the whole particle, while Bi and V also presented in the elemental maps, indicating the existence of  $\text{BiVO}_4$  in the  $\text{WO}_3/\text{BiVO}_4$  composite. The weight percentages of W, O, Bi, and V elements were estimated at 59.3 wt%, 17.5 wt%, 19.3 wt%, and 3.8 wt%, respectively. Furthermore, the high-resolution transmission electron microscope (HRTEM) images of the selected  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  nanoplates were conducted as shown in Fig. 5(c) and (d).

Fig. 5(c) shows the measured lattice fringes with interface spacings of 0.36 nm and 0.37 nm which corresponded to the (200) and (020) crystallographic planes of monoclinic  $\text{WO}_3$  crystal phase, respectively, suggesting that  $\text{WO}_3$  nanoplates have highly crystallized monoclinic structure. Fig. 5(d) shows the HRTEM of the composite  $\text{WO}_3/\text{BiVO}_4$ . It reveals that the lattice fringe with interface spacings of 0.36 nm and 0.37 nm, which belong to the  $\text{WO}_3$  monoclinic structure and additional lattice fringe with interface spacings of 0.30 and 0.47 nm that can be





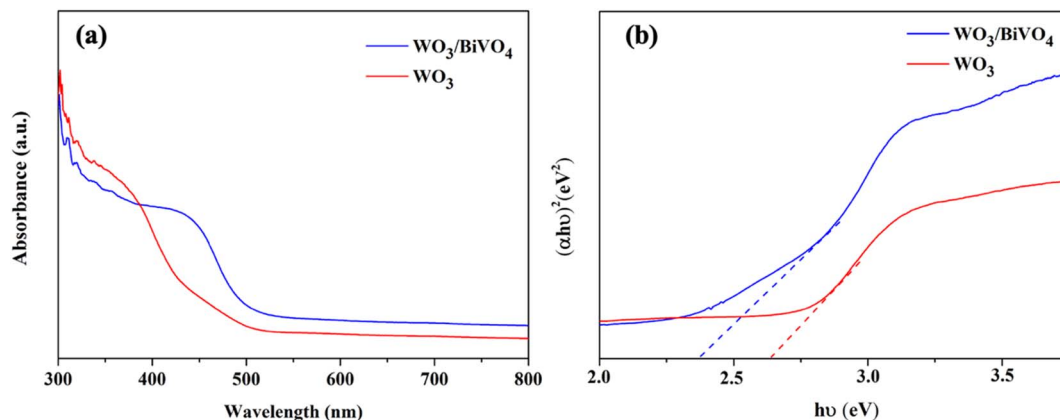


Fig. 4 (a) UV-Vis spectra and (b) energy bandgap of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.

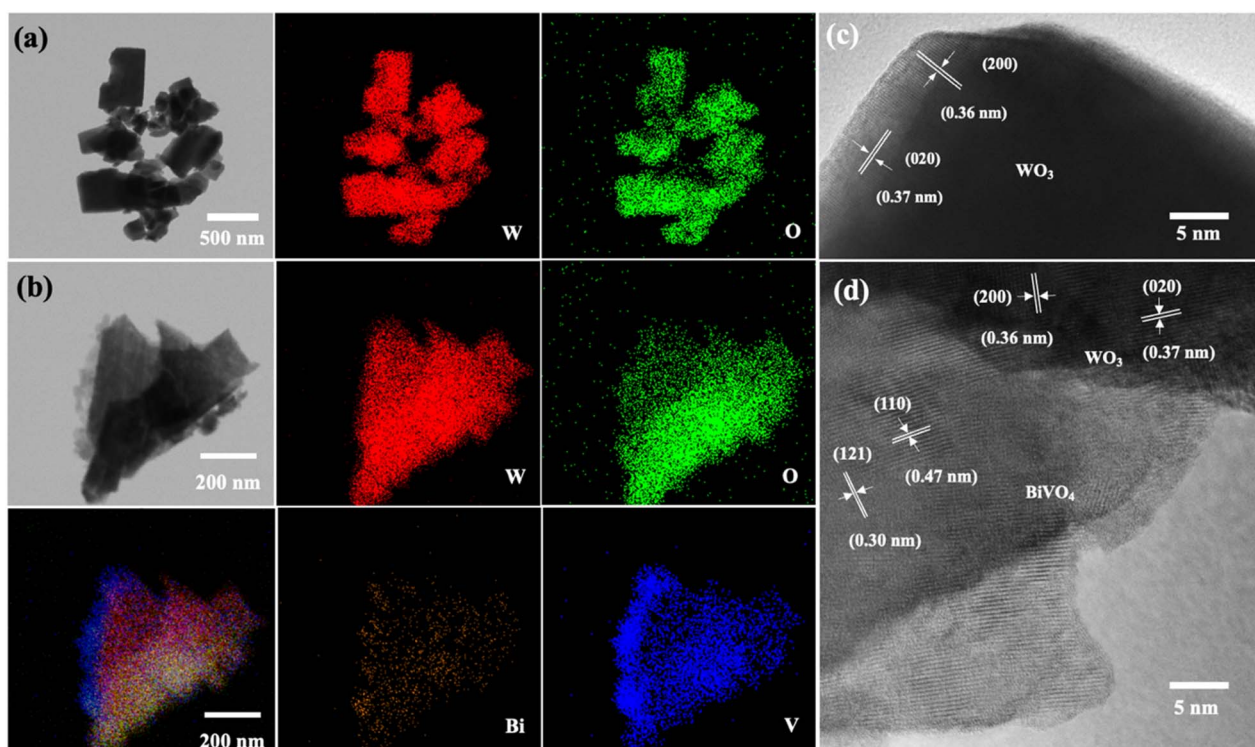


Fig. 5 TEM images and the corresponding EDS elemental mappings of (a) representative bare  $\text{WO}_3$  (b)  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes and HRTEM of (c)  $\text{WO}_3$  (d)  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.

ascribed to the (121) and (110) crystal planes of  $\text{BiVO}_4$ , respectively. These HRTEM results are in agreement with the XRD and confirm that  $\text{WO}_3$  nanoplates closely contact with  $\text{BiVO}_4$ .

### Photoelectrochemical performance

The PEC performance of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes was evaluated by measuring the transient photocurrent response ( $I-t$  curve) in the presence of 0.5 M  $\text{Na}_2\text{SO}_4$  and an equal concentration of  $\text{Na}_2\text{SO}_4$  and glycerol at 0.5 M electrolyte at the applied potential of 1.23 V (vs. RHE) under simulated AM 1.5 G illumination as shown in Fig. 6(a and b). Fig. 6(a) shows

the photocurrent density of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes in presence of 0.5 M  $\text{Na}_2\text{SO}_4$  electrolyte. The pristine  $\text{WO}_3$  photoelectrode photocurrent density is  $2.40 \text{ mA cm}^{-2}$  which is comparable to other reported PEC systems of  $\text{WO}_3$  photoelectrode.<sup>29,31,32</sup> Interestingly, the photocurrent density of the  $\text{WO}_3/\text{BiVO}_4$  photoelectrode increases to  $5.12 \text{ mA cm}^{-2}$ , approximately 2 times higher than that of the pristine  $\text{WO}_3$  photoelectrode. The improved photocurrent density of  $\text{WO}_3/\text{BiVO}_4$  photoelectrode could be attributed to a synergistic effect of the crystal structure, light absorption, and charge separation. First, the monoclinic structure of  $\text{WO}_3$  and the monoclinic scheelite structure of  $\text{BiVO}_4$  provide fast electron transport and



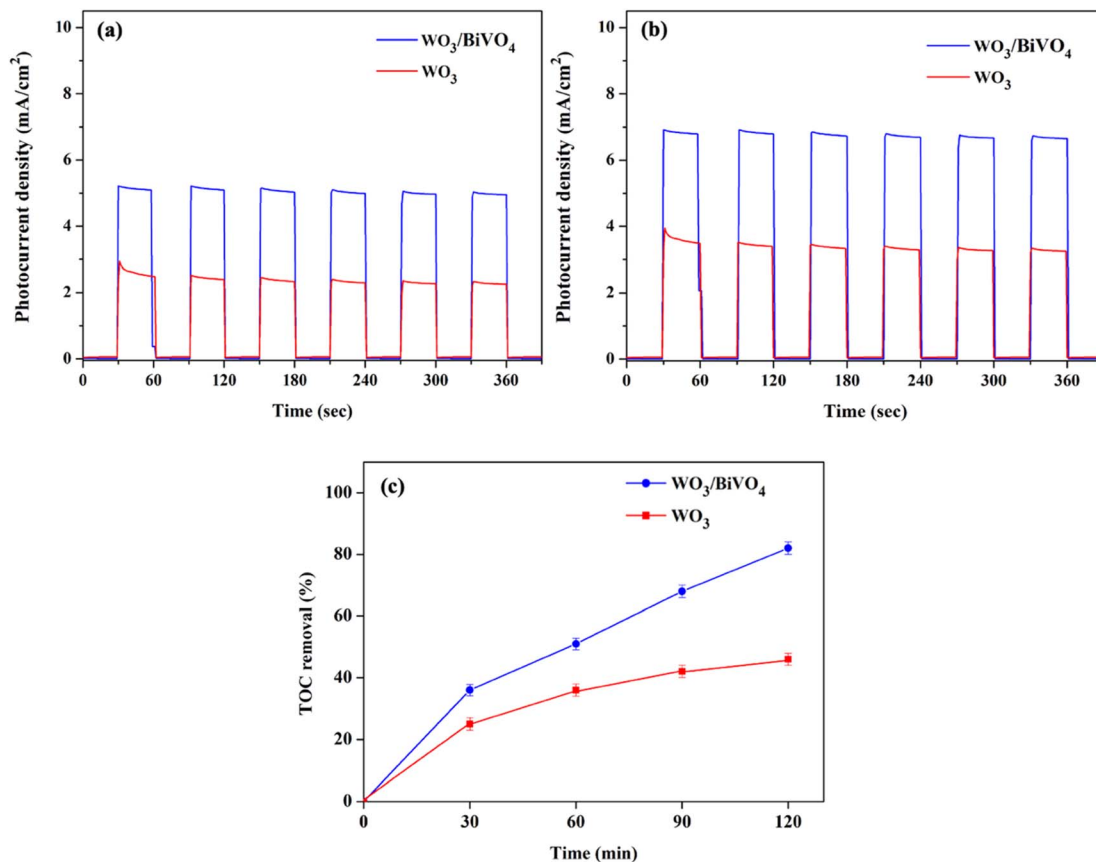


Fig. 6 Transient photocurrent response ( $I-t$ ) of WO<sub>3</sub> and WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes in the presence of (a) 0.5 M Na<sub>2</sub>SO<sub>4</sub> (b) 0.5 M Na<sub>2</sub>SO<sub>4</sub> + 0.5 M glycerol at 1.23 V vs. RHE under simulated AM 1.5 G illumination and (c) TOC removal efficiency of glycerol.

superior photocatalytic activity, respectively. Second, the light absorption of WO<sub>3</sub>/BiVO<sub>4</sub> samples as shown in Fig. 4(a) that the absorption range was extended to around 520 nm compared to WO<sub>3</sub> nanoplates that have the main absorption edge around 470 nm. Thus, good absorption in the visible light region can facilitate the enhancement of PEC properties under visible light irradiation.<sup>31</sup> Third, the WO<sub>3</sub>/BiVO<sub>4</sub> forms a type-II heterostructure which effectively reduces charge recombination by facilitating electron separation between WO<sub>3</sub> and BiVO<sub>4</sub>.<sup>32,38</sup> In addition, the oxygen vacancy presence in WO<sub>3</sub>/BiVO<sub>4</sub> from the XPS analysis as shown in Fig. 3(b) can increase the driving force for charge separation of WO<sub>3</sub>/BiVO<sub>4</sub>.<sup>31,38</sup> To further improve the performance and additional functionality of PEC for H<sub>2</sub> production and waste degradation, glycerol was added to the Na<sub>2</sub>SO<sub>4</sub> electrolyte to generate a bifunctional PEC system. It has been reported that small organic molecules such as glycerol waste can act as a sacrificial agent and electron donor, promoting the photocatalytic water splitting performance.<sup>42,43</sup> As shown in Fig. 6(b), the photocurrent density of WO<sub>3</sub> and WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes in presence of a mixture of 0.5 M Na<sub>2</sub>SO<sub>4</sub> and 0.5 M glycerol electrolyte is substantially increased. The photocurrent response of bare WO<sub>3</sub> photoelectrode is 3.41 mA cm<sup>-2</sup> and increases to 6.85 mA cm<sup>-2</sup> for WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes. Interestingly, the photocurrent response of WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes in the presence of Na<sub>2</sub>SO<sub>4</sub> and glycerol in

an electrolyte compared to that of WO<sub>3</sub> photoelectrode in the presence of only Na<sub>2</sub>SO<sub>4</sub> was increased by 2.8 times. The superior performance of WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes is due to the above-mentioned reasons and possibly due to the hydroxy group, which provides trapping for photoexcited holes and creates reactive hydroxyl radical (OH<sup>•</sup>) that effectively oxidize organic molecule,<sup>37</sup> from FTIR analysis as shown in Fig. 2(b). In addition, Fig. 6(c) shows the TOC removal by WO<sub>3</sub> and WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes. This can be seen that the TOC removal of WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes substantially increased and reached 82%, while WO<sub>3</sub> photoelectrodes gradually increased and reached 40%. Thus, the WO<sub>3</sub>/BiVO<sub>4</sub> photoelectrodes provide efficient charge transfer and separation, which in turn contribute to both effective PEC water splitting and contaminant degradation.

Based on the above discussions, the mechanism of the dual functional PEC system of photoelectrode is illustrated in Fig. 7, the conduction band (CB) of BiVO<sub>4</sub> is close to the hydrogen-reduction potential and the photo-excited electrons can thermodynamically transfer from the high CB energy level of BiVO<sub>4</sub> to the more positive CB of WO<sub>3</sub>. Holes in the valence band (VB) of WO<sub>3</sub> can move spontaneously to the VB of BiVO<sub>4</sub> for water oxidation. These bandgap differences between WO<sub>3</sub> and BiVO<sub>4</sub> also enhance the charge separation and reduce the bulk's charge recombination rate. As a result, the WO<sub>3</sub>/BiVO<sub>4</sub>

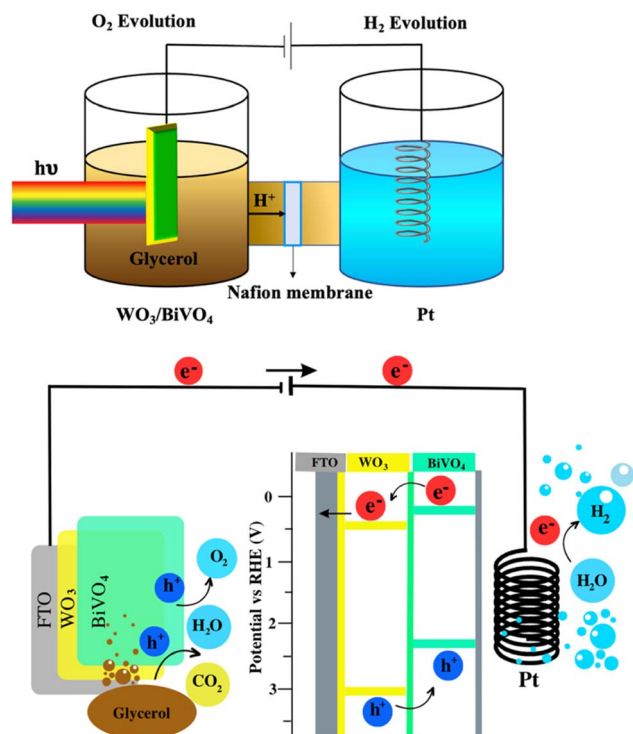


Fig. 7 Schematic visualization of the bifunctional PEC system (hydrogen generation and glycerol degradation) using H-cell type PEC reactor.

photoelectrodes exhibit much better PEC performance than that of the bare  $\text{WO}_3$  photoelectrode.

## Experimental section

### Synthesis of $\text{WO}_3$ and $\text{WO}_3/\text{BiVO}_4$ photoelectrodes

Fig. 8 shows the preparation of  $\text{WO}_3$  and  $\text{WO}_3/\text{BiVO}_4$  photoanodes by a hydrothermal method. Firstly, 0.1 g of sodium tungstate dihydrate ( $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$ ) was dissolved in 10 mL of Milli-Q water. Then, 3 mL of 2 M of hydrochloric acid (HCl) was added dropwise in the above solution under constant stirring at room temperature for 15 min. Subsequently, 0.2 g of citric acid ( $\text{C}_6\text{H}_8\text{O}_7$ ) and 15 mL of Milli-Q water were added into the mixture with continual stirring for 20 min. Afterward, 30 mL of the prepared precursor solution was then transferred to a 50 mL Teflon-lined stainless-steel autoclave. Before immersing FTO glass into the autoclave, FTO glass substrate was cleaned by ultrasonic treatment using acetone, ethanol, and isopropanol (each for 15 min), followed by drying in a nitrogen stream. After

the FTO glass was immersed in an autoclave with the FTO side leaned down against the wall, the autoclave was sealed and kept at 120 °C for 8 h. After the hydrothermal process, the samples were rinsed with Milli-Q water, and dried in a nitrogen stream. Finally,  $\text{WO}_3$  photoelectrodes were obtained after annealing in air at 500 °C for 1 h. For  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes, the precursor of  $\text{BiVO}_4$  was prepared by dissolving 1.4 g of bismuth(III) nitrate pentahydrate ( $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ ), 0.8 g of vanadium acetylacetonate ( $\text{C}_{10}\text{H}_{14}\text{O}_5\text{V}$ ), 1 mL of acetic ( $\text{CH}_3\text{COOH}$ ), and 19 mL of acetylacetone ( $\text{C}_5\text{H}_8\text{O}_2$ ) with sonication until the solution's color changed to dark green. Then, the prepared  $\text{WO}_3$  photoelectrode was immersed into the  $\text{BiVO}_4$  precursor solution for 30 min. Afterward, the above sample was annealed in air at 450 °C for 3 h to obtain the  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.

### Characterization

The surface morphology of the as-prepared photoelectrodes were examined using a field emission scanning electron microscope (FE-SEM, JSM-7610FPlus, JEOL, Tokyo, Japan). Transmission electron microscope equipped with an energy-dispersive X-ray spectroscope (TEM/EDX) and high-resolution TEM (HRTEM) analyses were conducted by JEOL2100 Plus, operated at 200 keV. The crystalline phases of the photoanodes were characterized by X-ray diffraction (XRD; Bruker, D8 Discover, Germany) using the  $\text{Cu K}\alpha$  radiation in a  $2\theta$  range of 20°–80°. The functional group of the photoelectrodes were analyzed by FTIR spectroscopy and recorded over a region of 4000–650  $\text{cm}^{-1}$  (Nicolet 6700, Thermo Scientific, USA). Raman spectra were recorded over a spectral range of 200–1000  $\text{cm}^{-1}$  and collected on a Horiba XploRA PLUS instrument, Japan. The elemental states were analyzed by X-ray photon spectroscopy (XPS, Kratos AXIS Ultra DLD). The light absorption spectra were investigated by a UV-Vis spectrophotometer (JASCO V-630).

### Photoelectrochemical measurement

The dual functional PEC measurements were performed in an H-cell type PEC cell with a quartz window and tested on a CHI 660D electrochemical workstation. The prepared photoelectrodes, a Pt wire (1 mm diameter), and a Ag/AgCl electrode served as the working electrode, counter electrode, and reference electrode, respectively. The illumination area was set by an aperture diameter of 1 cm. A xenon lamp (100 W, Newport LCS-100) was used to simulate sunlight and the photocurrent densities were measured under solar AM 1.5 G. The PEC behaviour of the electrodes was characterized with degradation of 100 mL of a mixture of 0.5 M glycerol and 0.5 M  $\text{Na}_2\text{SO}_4$ .

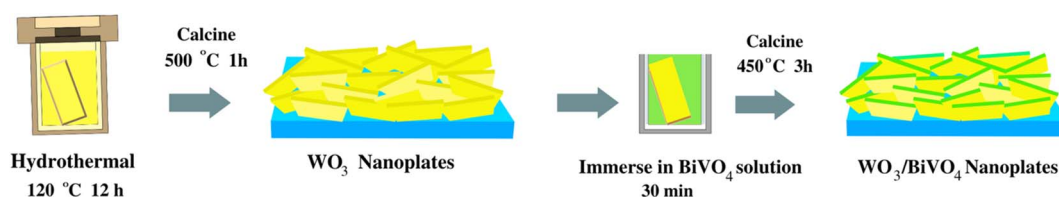


Fig. 8 Schematic figure summarizing the fabrication processes for synthesizing  $\text{WO}_3/\text{BiVO}_4$  photoelectrodes.





solution at room temperature. All solutions were prepared from Milli-Q water. The solutions were purged with nitrogen gas for 30 min prior to PEC measurement. To evaluate the degradation of glycerol, 5 mL of the treated solution was sampling every 30 min and analyzed by a Shimadzu TOC-V CPN Total Organic Carbon Analyzer. A 150 W Xe lamp light source with the intensity of the simulated 1-Sun solar illumination condition ( $AM\ 1.5$ ,  $100\ mW\ cm^{-2}$ ) illuminated at the immersed photo-electrode in the solution. Potentials *versus* RHE were calculated using the Nernst equation  $E_{RHE} = E_{Ag/AgCl} + 0.0591(pH) + 0.1976\ V$ .

## Conclusion

In summary, a simple hydrothermal technique is developed for fabricating the heterojunction  $WO_3/BiVO_4$  photoanodes. The  $WO_3/BiVO_4$  photoanodes take advantage of both the superior electron transport of the monoclinic structure of  $WO_3$  and the good photocatalytic activity of the monoclinic scheelite structure of  $BiVO_4$ . The photocatalytic activity of the pristine  $WO_3$  and  $WO_3/BiVO_4$  photoanodes are  $2.40\ mA\ cm^{-2}$  and  $5.12\ mA\ cm^{-2}$  in the presence of  $0.5\ M\ Na_2SO_4$  electrolyte, respectively. The improved photocurrent density of  $WO_3/BiVO_4$  photo-electrode could be attributed to a synergistic effect of the superior crystal structure, type-II heterostructure, and the presence of oxygen vacancies. Furthermore, the photocurrent density of  $WO_3/BiVO_4$  photoelectrodes was improved to  $6.85\ mA\ cm^{-2}$  and the TOC removal efficiency reached about 82%, in the presence of a mixture of  $0.5\ M\ Na_2SO_4$  and  $0.5\ M$  glycerol electrolyte. The photocurrent density of the  $WO_3/BiVO_4$  photo-electrodes is about 2.8 times higher than that of the pristine  $WO_3$  in the presence of  $0.5\ M\ Na_2SO_4$  electrolyte. The considerable enhancement is due to the afore-mentioned synergistic effects and the hydroxy group that provides trapping for photoexcited holes and creates reactive hydroxyl radicals ( $OH^\bullet$ ) that effectively oxidizes organic molecules.

## Author contributions

“Conceptualization, P. P., J.-H. Y., T. B., and S. T.; methodology, P. P., and S. T.; validation, P. P., J.-H. Y., T. B., M. L., C. T., and S. T.; formal analysis, P. P., J.-H. Y., T. B., M. L., C. T., and S. T.; investigation, P. P., J.-H. Y., T. B., M. L., and S. T.; resources, P. P., T. B., C. T., and S. T.; visualization, P. P.; writing—original draft preparation, P. P., and S. T.; writing—review and editing, P. P., J.-H. Y., T. B., M. L., C. T., and S. T.; and supervision, S. T. All authors have read and agreed to the published version of the manuscript.”

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research project was supported by Mahidol University (grant no. IO 864152050000). Partial financial support from

National Nanotechnology Center (NANOTEC), National Science and Technology Development Agency (NSTDA) (grant no. P1951553), is also appreciated. The authors would like to acknowledge the Faculty of Environment and Resource Studies, and Mahidol University-Frontier Research Facility (MU-FRF), Mahidol University and National Nanotechnology Center (NANOTEC, Thailand) for providing the experimental facilities and technical support.

## References

- 1 A. Syafiuddin, J. H. Chong, A. Yuniarto and T. Hadibarata, *Bioresour. Technol. Rep.*, 2020, **12**, 100608.
- 2 S. Hu, X. Luo, C. Wan and Y. Li, *J. Agric. Food Chem.*, 2012, **60**, 5915–5921.
- 3 Z. Gholami, A. Z. Abdullah and K.-T. Lee, *Renewable Sustainable Energy Rev.*, 2014, **39**, 327–341.
- 4 J. A. Siles, M. A. Martín, A. F. Chica and A. Martín, *Bioresour. Technol.*, 2010, **101**, 6315–6321.
- 5 Y. Li and J. Z. Zhang, *Laser Photonics Rev.*, 2010, **4**, 517–528.
- 6 S. Wang, G. Dai, H. Yang and Z. Luo, *Prog. Energy Combust. Sci.*, 2017, **62**, 33–86.
- 7 S. Abanades, *ChemEngineering*, 2019, **3**, 63.
- 8 K. Nie, X. Qu, D. Gao, B. Li, Y. Yuan, Q. Liu, X. Li, S. Chong and Z. Liu, *ACS Appl. Mater. Interfaces*, 2022, **14**, 19847–19856.
- 9 Z. Liu, K. Nie, X. Qu, X. Li, B. Li, Y. Yuan, S. Chong, P. Liu, Y. Li, Z. Yin and W. Huang, *J. Am. Chem. Soc.*, 2022, **144**, 4863–4873.
- 10 Z. Liu, K. Nie, Y. Yuan, B. Li, P. Liu, S. Chong, Y. Du and W. Huang, *CCS Chem.*, 2022, **4**, 3391–3401.
- 11 P. J. Megía, A. J. Vizcaino, J. A. Calles and A. Carrero, *Energy Fuels*, 2021, **35**, 16403–16415.
- 12 M. Xiao, B. Luo, S. Thaweesak and L. Wang, *Prog. Nat. Sci.: Mater. Int.*, 2018, **28**, 189–193.
- 13 W. Yang, R. R. Prabhakar, J. Tan, S. D. Tilley and J. Moon, *Chem. Soc. Rev.*, 2019, **48**, 4979–5015.
- 14 Y. Yang, S. Niu, D. Han, T. Liu, G. Wang and Y. Li, *Adv. Energy Mater.*, 2017, **7**, 1700555.
- 15 A. Fujishima and K. Honda, *Nature*, 1972, **238**, 37–38.
- 16 P. Peerakiatkhajohn, J.-H. Yun, T. Butburee, W. Nissapa and S. Thaweesak, *RSC Adv.*, 2022, **12**, 2652–2661.
- 17 T. Butburee, Y. Bai and L. Wang, *J. Mater. Chem. A*, 2021, **9**, 23313–23322.
- 18 C. Phawa, S. Prayoonpokarach, K. Sinthiptharakoon, P. Chakhranont, W. Sangkhun, K. Faungnawakij and T. Butburee, *ChemCatChem*, 2020, **12**, 2116–2124.
- 19 P. Peerakiatkhajohn, T. Butburee, J.-H. Sul, S. Thaweesak and J.-H. Yun, *Nanomaterials*, 2021, **11**, 1059.
- 20 S. Wang, H. Chen, G. Gao, T. Butburee, M. Lyu, S. Thaweesak, J.-H. Yun, A. Du, G. Liu and L. Wang, *Nano Energy*, 2016, **24**, 94–102.
- 21 P. Dias, T. Lopes, L. Meda, L. Andrade and A. Mendes, *Phys. Chem. Chem. Phys.*, 2016, **18**, 5232–5243.
- 22 Z. Zhao, T. Butburee, P. Peerakiatkhajohn, M. Lyu, S. Wang, L. Wang and H. Zheng, *ChemistrySelect*, 2016, **1**, 2772–2777.





- 23 X. Zong, S. Thaweesak, H. Xu, Z. Xing, J. Zou, G. Lu and L. Wang, *Phys. Chem. Chem. Phys.*, 2013, **15**, 12314–12321.
- 24 P. Peerakiatkhajohn, J.-H. Yun, H. Chen, M. Lyu, T. Butburee and L. Wang, *Adv. Mater.*, 2016, **28**, 6405–6410.
- 25 P. Peerakiatkhajohn, J.-H. Yun, T. Butburee, H. Chen, S. Thaweesak, M. Lyu, S. Wang and L. Wang, *J. Hazard. Mater.*, 2021, **402**, 123533.
- 26 S. Wang, X. Wang, B. Liu, Z. Guo, K. Ostrikov, L. Wang and W. Huang, *Nanoscale*, 2021, **13**, 17989–18009.
- 27 M. Tayebi and B.-K. Lee, *Renewable Sustainable Energy Rev.*, 2019, **111**, 332–343.
- 28 F. Yi, J. Ma, C. Lin, H. Zhang, Y. Qian, H. Jin and K. Zhang, *Chem. Eng. J.*, 2022, **427**, 132028.
- 29 S. Y. Chae, C. S. Lee, H. Jung, O.-S. Joo, B. K. Min, J. H. Kim and Y. J. Hwang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 19780–19790.
- 30 S. Thaweesak, M. Lyu, P. Peerakiatkhajohn, T. Butburee, B. Luo, H. Chen and L. Wang, *Appl. Catal., B*, 2017, **202**, 184–190.
- 31 J. Liu, W. Chen, Q. Sun, Y. Zhang, X. Li, J. Wang, C. Wang, Y. Yu, L. Wang and X. Yu, *ACS Appl. Energy Mater.*, 2021, **4**, 2864–2872.
- 32 P. Wei, Y. Wen, K. Lin and X. Li, *Int. J. Hydrogen Energy*, 2021, **46**, 27506–27515.
- 33 Y. Cao, Z. Xing, B. Wang, W. Tang, R. Wu, J. Li and M. Ma, *Catalysts*, 2020, **10**, 556.
- 34 M. G. Mali, H. Yoon, M.-w. Kim, M. T. Swihart, S. S. Al-Deyab and S. S. Yoon, *Appl. Phys. Lett.*, 2015, **106**, 151603.
- 35 M. A. Butler, *J. Appl. Phys.*, 1977, **48**, 1914–1920.
- 36 S. Tokunaga, H. Kato and A. Kudo, *Chem. Mater.*, 2001, **13**, 4624–4628.
- 37 B. Ben Salem, G. Essalah, S. Ben Ameer, B. Duponchel, H. Guermazi, S. Guermazi and G. Leroy, *RSC Adv.*, 2023, **13**, 6287–6303.
- 38 Y. Wang, W. Tian, L. Chen, F. Cao, J. Guo and L. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 40235–40243.
- 39 S. S. Kalanur, *Catalysts*, 2019, **9**, 456.
- 40 S. Wang, P. Chen, Y. Bai, J.-H. Yun, G. Liu and L. Wang, *Adv. Mater.*, 2018, **30**, 1800486.
- 41 S. S. M. Bhat, S. A. Lee, J. M. Suh, S.-P. Hong and H. W. Jang, *Appl. Sci.*, 2018, **8**, 1765.
- 42 D. I. Kondarides, V. M. Daskalaki, A. Patsoura and X. E. Verykios, *Catal. Lett.*, 2008, **122**, 26–32.
- 43 T. Butburee, P. Chakthranont, C. Phawa and K. Faungnawakij, *ChemCatChem*, 2020, **12**, 1873–1890.

