

Cite this: *J. Mater. Chem. A*, 2023, 11, 17056Received 23rd April 2023  
Accepted 26th June 2023

DOI: 10.1039/d3ta02405a

rsc.li/materials-a

## Unique Pd/PdO–In<sub>2</sub>O<sub>3</sub> heterostructures for the highly efficient detection of triethylamine†

Yumin Zhang,<sup>a</sup> Zongming Deng,<sup>a</sup> Jianhong Zhao,<sup>\*c</sup> Tong Zhou,<sup>a</sup> Alain R. Puente Santiago,<sup>ib</sup> Tianwei He,<sup>a</sup> Jin Zhang,<sup>a</sup> Qingju Liu<sup>ib</sup>\*<sup>a</sup> and Guangzhi Hu<sup>ib</sup>\*<sup>c</sup>

Triethylamine significantly harms the human body, so it is important to develop a triethylamine gas sensor with excellent performance for triethylamine detection. In this work, a Pd/PdO–In<sub>2</sub>O<sub>3</sub> triethylamine gas sensor is developed by a simple, low-cost method, which exhibits improved comprehensive performance for triethylamine detection, including high sensitivity, fast response/recovery time, good selectivity, long-term stability, and certain moisture resistance. The unique method simultaneously realizes Pd loading and multiple PdO–In<sub>2</sub>O<sub>3</sub> P–N heterojunctions, which accelerate the electron transport speed and increase electron transport channels, ultimately endowing Pd/PdO–In<sub>2</sub>O<sub>3</sub> with excellent triethylamine sensing performance. This provides new methods and insights for preparing high-performance triethylamine sensors.

## Introduction

Triethylamine (TEA) has a wide range of sources in daily life, it has a wide range of applications in the manufacturing process of many industrial products,<sup>1</sup> such as cosmetics and personal care products, some drugs and medical devices, manufacturing of polyurethane, resin, dye, preservatives, foaming agents, *etc.* During the production and use of these industrial products, a certain concentration of triethylamine will inevitably be generated. In addition, seafood will produce TEA during the decay process, the higher the concentration of TEA, the greater the degree of decay, so the degree of decay of seafood can be determined by detecting the concentration of TEA.<sup>2</sup>

TEA is volatile and studies have shown that once the human body inhales too much TEA gas, it will cause respiratory and blood system diseases and eye damage, long-term exposure to excessive TEA gas can easily cause asthma, emphysema, and even death.<sup>3,4</sup> The development of an efficient TEA detection method is of great significance for people's physical health. When it comes to high-efficiency detection of TEA, semiconductor gas sensors have attracted attention due to their low cost, portability, and high sensitivity. Research and application of high-performance TEA sensors are expected to effectively

monitor TEA gas in areas such as industrial pollution, seafood decay, indoor pollution, and medical fields (Fig. 1).

In the research of semiconductor TEA gas sensors, those based on different metal oxides have been widely studied, such as SnO<sub>2</sub>,<sup>5</sup> In<sub>2</sub>O<sub>3</sub>,<sup>6</sup> ZnO,<sup>7</sup> CuO,<sup>8</sup> *etc.* Among them, In<sub>2</sub>O<sub>3</sub> has been favored by researchers because of its good gas-sensing properties of TEA, however, there are still issues such as slow recovery time and high operating temperature.<sup>9</sup> For In<sub>2</sub>O<sub>3</sub>-based TEA gas-sensing material, the current research mainly focuses on controlling the morphology of In<sub>2</sub>O<sub>3</sub>,<sup>10</sup> doping with noble metals,<sup>11</sup> forming heterojunctions with other oxides,<sup>12</sup> *etc.*, wherein, the loading of Pd nanoparticles (NPs) is an effective method for modifying In<sub>2</sub>O<sub>3</sub>, where Pd NPs can influence the overall energy and catalytic activity, while also controlling the number of charge carriers (electrons and holes) in the suctor,<sup>13</sup> lowering the activation energy of the system and promoting electron transfer,<sup>14–16</sup> and ultimately improve the comprehensive gas sensing performance of In<sub>2</sub>O<sub>3</sub>.<sup>17–19</sup> In addition to the catalytic effect of Pd NPs that can effectively improve the gas sensitivity of In<sub>2</sub>O<sub>3</sub>, PdO also plays an important role in improving the gas sensitivity of In<sub>2</sub>O<sub>3</sub>, PdO is a P-type semiconductor, it is easy to form a P–N heterojunction when combined with N-type semiconductor In<sub>2</sub>O<sub>3</sub>, which will increase the thickness of the electron depletion layer (EDL) of the material and form a carrier transport channel, which will help to provide more adsorption and reaction sites, and ultimately improve the gas sensing performance.<sup>20,21</sup>

For gas-sensing materials, the number of active sites and electron transport channels, and the electron transport efficiency have important impacts on the gas-sensing performance,<sup>20,22</sup> so how to enhance the related properties has become a problem that researchers must face, and these properties can be improved through the preparation method of

<sup>a</sup>Yunnan Key Laboratory for Micro/Nano Materials & Technology, National Center for International Research on Photoelectric and Energy Materials, School of Materials and Energy, Yunnan University, Kunming 650091, China. E-mail: qjliu@ynu.edu.cn

<sup>b</sup>Walker Department of Mechanical Engineering, The University of Texas at Austin, Austin, TX, 78712, USA

<sup>c</sup>Institute for Ecological Research and Pollution Control of Plateau Lakes, School of Ecology and Environmental Science, Yunnan University, Kunming 650091, China. E-mail: zhaojianhong@ynu.edu.cn; guangzhihu@ynu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ta02405a>

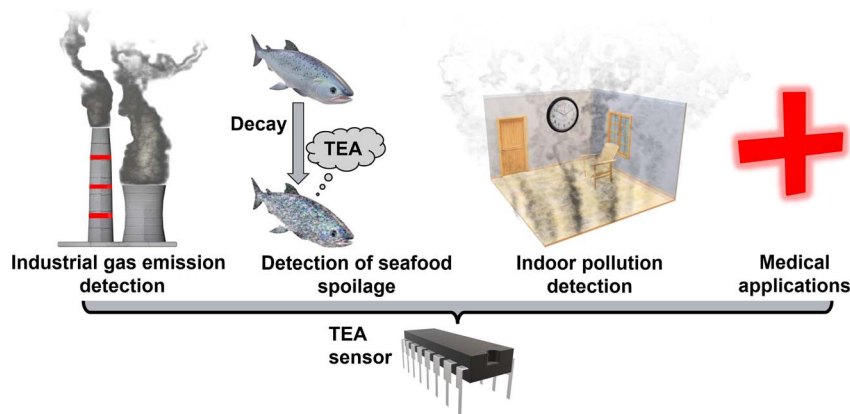


Fig. 1 Application of TEA sensor.

materials. Among the current common Pd species loading methods, the common ones are  $\text{NaBH}_4$  reduction method,<sup>17</sup> ultraviolet light reduction method,<sup>23</sup> one-pot method,<sup>24</sup> *etc.* These methods have their own advantages, and the Pd species loaded by these methods mainly play the role of surface modification or lattice doping, which promote the gas sensing performance by affecting the carrier distribution, reducing the reaction activation energy<sup>20</sup> and increasing the active sites and electron transport channels. Although surface modification and lattice doping play a positive role, however, they cannot affect the specific surface area (SSA) and pore structure of the base material, which is closely related to the gas sensing performance. In addition, if the preparation time is too long, it is easy to occur the poisoning of precious metals, which is easy to lead to the reduction of the material's activity or even inactivation.<sup>20</sup>

In this study, Pd/PdO- $\text{In}_2\text{O}_3$  gas-sensing material were successfully prepared by a simple precursor-loaded Pd species and combined with a subsequent pyrolysis strategy, and exhibited excellent gas-sensing performance for TEA. Compared with  $\text{NaBH}_4$ -reduced Pd- $\text{In}_2\text{O}_3$  gas-sensing material prepared in this study, Pd/PdO- $\text{In}_2\text{O}_3$  showed higher TEA

sensitivity and faster response/recovery (res/rec) speed. Further analysis and characterization found that this unique precursor doping method causes Pd species to be oxidized to PdO during the pyrolysis process of the precursor, and due to the phase change and high temperature of the precursor, the Pd species distributed only on the surface of the precursor enters between the  $\text{In}_2\text{O}_3$  nanoparticles and forms PdO, which not only forms a large number of P-N heterojunctions (PdO- $\text{In}_2\text{O}_3$ ) to accelerate electron transport, but also, PdO surrounded by  $\text{In}_2\text{O}_3$  nanoparticles has the opportunity to form numerous electron transport channels and active sites to improve the gas sensing performance. At the same time, the stable property of PdO can effectively avoid the occurrence of noble metal poisoning and help to improve the long-term stability of the sensors. The current research ideas can further expand its scope of application and have reference significance for future related research.

## Experimental section

As depicted in Fig. 2a, Pd species were loaded using two different methods (method 1: commonly used  $\text{NaBH}_4$  reduction

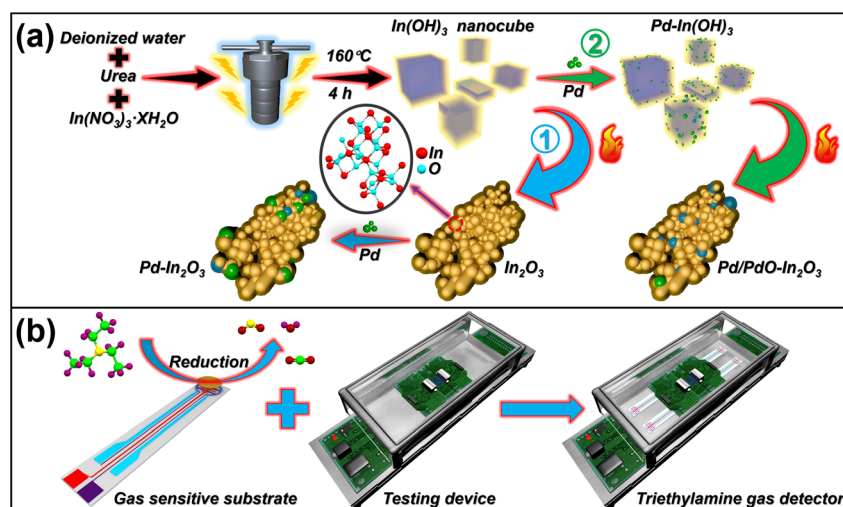


Fig. 2 (a) Preparation process of Pd- $\text{In}_2\text{O}_3$  and Pd/PdO- $\text{In}_2\text{O}_3$ , (b) sensor and performance testing device.

method, method 2: precursor loading method). Fig. 2b shows a simple schematic diagram of the sensor and its performance testing device, the detailed schematics can be found in Fig. S1,† with detailed experimental details, analysis and the preparation process of the gas sensor can be obtained in the ESI.†

## Results and discussion

### Structural and morphological characteristics

First, the phase structures of the corresponding samples were analyzed using X-ray diffraction (XRD). As illustrated in Fig. 3a, the as-prepared  $\text{In}(\text{OH})_3$  exhibits a narrow and sharp diffraction peak that corresponds to the PDF standard card PDF#76-1463, indicating high crystallinity and large grain size, there is no noticeable impurity peak, suggesting that the sample has high purity. Upon calcination of the  $\text{In}(\text{OH})_3$  precursor, the phase structure undergoes a change, and  $\text{In}(\text{OH})_3$  is dehydrated into  $\text{In}_2\text{O}_3$ , from Fig. 3a, the four strongest peaks correspond to the PDF standard card PDF#71-2195 of  $\text{In}_2\text{O}_3$ , corresponding to the (222), (400), (440), (622) crystal planes, and also have narrow and sharp diffraction peaks, indicating that good crystallinity. At the same time, we analyzed the XRD patterns of Pd/PdO- $\text{In}_2\text{O}_3$  after loading Pd, it can be seen from Fig. 3b that the XRD curves of Pd/PdO- $\text{In}_2\text{O}_3$  with different loadings did not change significantly, which indicated that during the functionalization process, the phase of  $\text{In}_2\text{O}_3$  is hardly affected.

The morphology and structure of the samples were characterized. Fig. 4a is the scanning electron microscope (SEM) image of the  $\text{In}(\text{OH})_3$  precursor, the SEM image shows that  $\text{In}(\text{OH})_3$  exhibits a micro-nano cube structure, and the thermal gravimetric image of  $\text{In}(\text{OH})_3$  (Fig. S2†) shows that  $\text{In}(\text{OH})_3$  has no significant mass change after 350 °C, so we use 350 °C as the annealing temperature of the sample. Since  $\text{In}(\text{OH})_3$  cubes are thermally decomposed into  $\text{In}_2\text{O}_3$  and  $\text{H}_2\text{O}$ ,  $\text{In}(\text{OH})_3$  nanocubes transform into  $\text{In}_2\text{O}_3$  nanorods (Fig. 4b). The SEM images of Pd/PdO- $\text{In}_2\text{O}_3$  (Fig. 4c) shows no significant changes compared to  $\text{In}_2\text{O}_3$ , both exhibited a nanorod morphology at the microscopic level, this indicates that the modification of  $\text{In}_2\text{O}_3$  by Pd/PdO did not cause major damage to its morphology, however, the uniformity of Pd/PdO- $\text{In}_2\text{O}_3$  was not as good as that of  $\text{In}_2\text{O}_3$ .

To analyze the differences between Pd- $\text{In}_2\text{O}_3$  and Pd/PdO- $\text{In}_2\text{O}_3$ , we further analyzed the transmission electron microscope (TEM) images of the samples. First, we tested the TEM and high-resolution TEM (HRTEM) images of Pd- $\text{In}_2\text{O}_3$ . Fig. 4d-f shows that Pd nanoparticles are almost all distributed on the surface of  $\text{In}_2\text{O}_3$  nanorods (this can be predicted from the loading method of Pd nanoparticles, because Pd nanoparticles are directly reduced by  $\text{NaBH}_4$ , so Pd nanoparticles are only distributed on the surface of  $\text{In}_2\text{O}_3$  (ref. 17 and 25)), which mainly play a role in surface modification of  $\text{In}_2\text{O}_3$  nanorods, the selected area electron diffraction (SAED) of 0.8% Pd- $\text{In}_2\text{O}_3$  showed obvious polycrystalline diffraction rings (Fig. 4d inset), indicating excellent crystallinity. For Pd/PdO- $\text{In}_2\text{O}_3$ , due to the effect of annealing in air, most of the Pd species exist in the form of PdO. To observe the distribution of PdO in  $\text{In}_2\text{O}_3$ , we used high-angle annular dark-field STEM (HAADF-STEM) to characterize the samples, from Fig. 4h, it can be seen that there is almost no surface distribution of Pd nanoparticles, when the image is further enlarged, the presence of PdO can be observed (Fig. 4i and j), and PdO is surrounded by  $\text{In}_2\text{O}_3$  nanoparticles, and an obvious multiple heterostructure is formed between PdO and  $\text{In}_2\text{O}_3$  (shown by the red dotted line in Fig. 4i and j).

The SSA and pore size of the prepared samples were analyzed (Fig. 5a-c), the results showed a significant increase in the Brunauer-Emmett-Teller (BET) SSA of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  (Fig. 5c) compared to  $\text{In}_2\text{O}_3$  (Fig. 5a) and 0.8% Pd- $\text{In}_2\text{O}_3$  (Fig. 5b) ( $67.58 \text{ m}^2 \text{ g}^{-1}$  for 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ , compared to  $48.75 \text{ m}^2 \text{ g}^{-1}$  for  $\text{In}_2\text{O}_3$  and  $50.69 \text{ m}^2 \text{ g}^{-1}$  for 0.8% Pd- $\text{In}_2\text{O}_3$ ). And the average pore size (APS) was significantly reduced ( $8.44 \text{ nm}$  for 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  (Fig. 5c inset),  $13.40 \text{ nm}$  for  $\text{In}_2\text{O}_3$  (Fig. 5a inset),  $13.09 \text{ nm}$  for 0.8% Pd- $\text{In}_2\text{O}_3$  (Fig. 5b inset)). The increase of the SSA and the decrease of the pore size mean that the size/agglomeration of the  $\text{In}_2\text{O}_3$  nanoparticles has changed, which indicates that the addition of PdO altered the size/agglomeration of  $\text{In}_2\text{O}_3$  nanoparticles. In contrast, there was no significant difference in the BET SSA and APS between  $\text{In}_2\text{O}_3$  and 0.8% Pd- $\text{In}_2\text{O}_3$ , indicating that the surface modification of Pd nanoparticles had little effect on the BET SSA and pore size of  $\text{In}_2\text{O}_3$ .

In conclusion, the Pd species of Pd- $\text{In}_2\text{O}_3$  and Pd/PdO- $\text{In}_2\text{O}_3$  have obvious distribution differences, and the Pd nanoparticles

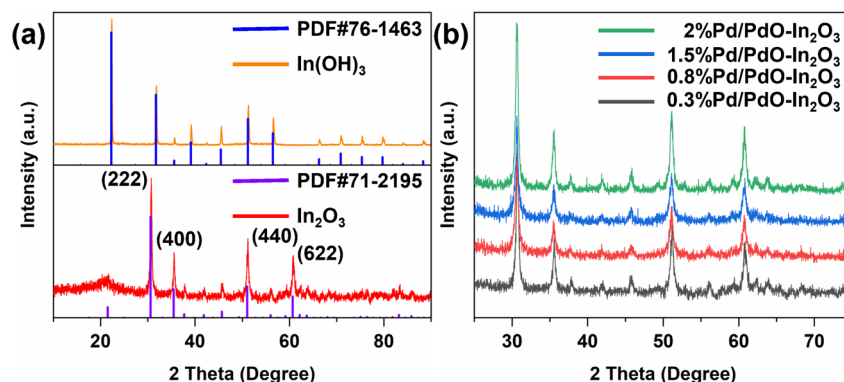


Fig. 3 (a) XRD images of  $\text{In}(\text{OH})_3$  and  $\text{In}_2\text{O}_3$  and their PDF standard cards compared, (b) XRD contrast images of  $\text{In}_2\text{O}_3$  with different Pd/PdO loadings.



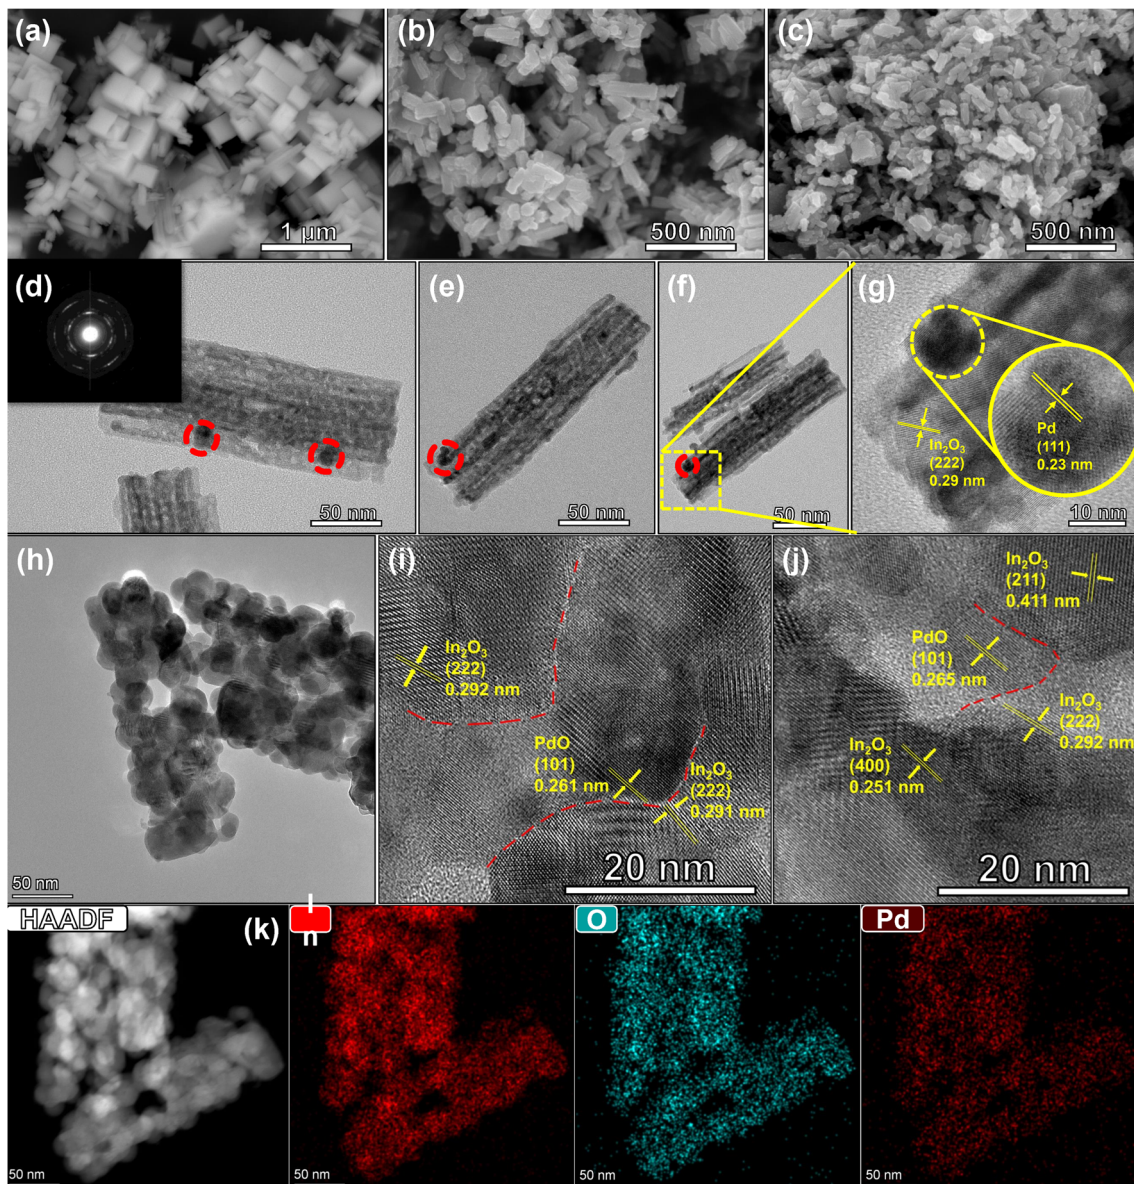


Fig. 4 SEM images of (a)  $\text{In}(\text{OH})_3$ , (b)  $\text{In}_2\text{O}_3$  nanorods, (c) 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  nanorods, (d)–(f) TEM images of 0.8% Pd- $\text{In}_2\text{O}_3$ , (g) HRTEM image of 0.8% Pd- $\text{In}_2\text{O}_3$ , (h)–(j) HAADF-STEM images of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ , (k) Mapping images of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ .

in Pd- $\text{In}_2\text{O}_3$  are randomly distributed on the surface of  $\text{In}_2\text{O}_3$  nanorods, which mainly play the role of surface modification for  $\text{In}_2\text{O}_3$  nanorods. For Pd/PdO- $\text{In}_2\text{O}_3$ , part of the PdO enters between the  $\text{In}_2\text{O}_3$  nanoparticles, forming multiple hetero-junction structures with the  $\text{In}_2\text{O}_3$  nanoparticles, which indicates that under the dual effects of  $\text{In}(\text{OH})_3$  phase transition and heat treatment, the Pd species is transformed into PdO, and the loading position changes, so that part of the Pd species that was only distributed on the surface of  $\text{In}(\text{OH})_3$  before is transformed into PdO that enters the gap between  $\text{In}_2\text{O}_3$  nanoparticles (Fig. 5d), this transformation not only changes the arrangement of  $\text{In}_2\text{O}_3$  nanoparticles, which is conducive to the formation of more electron transport channels, but also facilitates the formation of p-n heterojunction between PdO and  $\text{In}_2\text{O}_3$ , thereby accelerating the transport of carrier.<sup>26,27</sup>

X-ray photoelectron spectroscopy (XPS) spectra of different samples were tested and all peaks were calibrated using the C 1s peak at 284.8 eV. Fig. 6a is the XPS full-spectrum image of different samples, no obvious impurity peaks were found in all samples, indicating that the samples were not contaminated by impurity elements during the preparation process. For 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ , its Pd 3d spectrum can be almost all assigned to PdO, which indicates that heat treatment and air oxidation almost convert most of the Pd to PdO (Fig. 6b). For 0.8% Pd- $\text{In}_2\text{O}_3$ , the Pd 3d spectrum can be assigned to Pd and PdO (Fig. 6b), indicating that most of the Pd elements exist in the form of monovalent, which is consistent with the HRTEM image analysis results. For 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ , the electron spin coupling gap of In 3d is 7.58 eV (Fig. 6c), which indicates that the In element exists in the form of  $\text{In}_2\text{O}_3$ , notably,



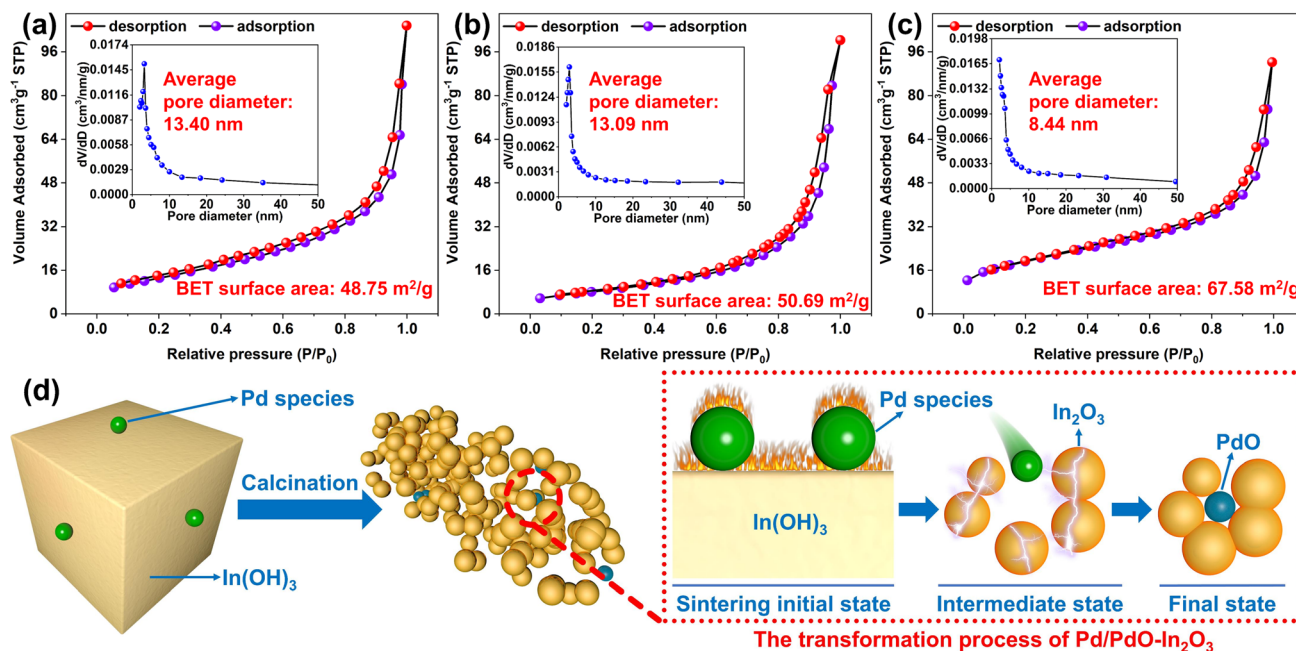


Fig. 5 Nitrogen adsorption/desorption and pore size distribution curves: (a)  $\text{In}_2\text{O}_3$  nanorods, (b) 0.8% Pd- $\text{In}_2\text{O}_3$  nanorods, (c) 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  nanorods. (d) Formation mechanism of PdO- $\text{In}_2\text{O}_3$  heterojunction.

compared to 0.8% Pd- $\text{In}_2\text{O}_3$ , the In 3d peak of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  shifted about 0.22 eV towards the low binding energy, this indicates an electron transfer from  $\text{In}_2\text{O}_3$  to PdO.<sup>28</sup> The O 1s spectra of  $\text{In}_2\text{O}_3$ , 0.8% Pd- $\text{In}_2\text{O}_3$ , 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  were compared (Fig. 6d), the results show that 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  has a higher adsorbed oxygen content, which can provide more reactive species for the gas-sensing reaction,<sup>29,30</sup> this is an important reason for the better gas-sensing performance of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ .

The mass fraction of Pd element in several groups of samples was determined by inductively coupled plasma optical emission spectrometer (ICP-OES) (Table S1†) analysis, and the results showed that the Pd content in 0.8% Pd- $\text{In}_2\text{O}_3$  was higher than that in 0.8% Pd/PdO- $\text{In}_2\text{O}_3$ , this may be due to phenomena such as solvent taking away part of the noble metal and thermal treatment losing noble metal in the process of material preparation, and the actual mass percentage of Pd in 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  is 0.42%.

### Gas-sensing performance

All gas sensitivity tests are carried out within the range of 30–50% RH (unless otherwise specified).

Fig. 7a summarizes the relationship between the response values of different sensors and the operating temperature. It can be seen that the response value of 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  reached the highest 1380 at 150 °C, and the response value of the Pd/PdO- $\text{In}_2\text{O}_3$  sensor is generally better than that of the Pd- $\text{In}_2\text{O}_3$  control group, and the response value of the Pd- $\text{In}_2\text{O}_3$  sensor has no obvious change compared with the response value of the  $\text{In}_2\text{O}_3$  sensor, which means that the surface modification of Pd nanoparticles failed to effectively enhance the sensitivity of

$\text{In}_2\text{O}_3$  to TEA, however, its recovery characteristics were improved (Fig. S3†). Fig. 7b shows that the res/rec time of the 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  sensor is 30 s/90 s at a high response of 1380, showing a fast res/rec rate, this has a positive effect on the real-time detection of the sensor. The 0.8% Pd- $\text{In}_2\text{O}_3$  sensor has a response value of 215 to 10 ppm TEA at the optimal operating temperature and a res/rec time of 99 s/341 s (Fig. 7c), its response value and res/rec time are lower than 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  sensor.

The response-time curves of the sensor to different concentrations of TEA were tested (Fig. 7d) to study the TEA concentration test range of the 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  sensor, Fig. 7d shows that the sensor has a strong and rapid response to 1–100 ppm of TEA. When the TEA concentration increases to 100 ppm, the response value of the sensor does not increase significantly compared to 50 ppm. At the same time, we have performed a linear fitting on the response value of 1–50 ppm, it shows that the sensor has a good linear relationship of response value in the concentration range of 1–50 ppm TEA (Fig. 7d illustration). A low concentration of TEA was tested, and Fig. 7e shows that the sensor still has a certain response value to 0.1 ppm TEA, combined with Fig. 7d, it shows that the detection limit of the sensor is 0.1–100 ppm.

It can be observed from Fig. 8a that the response value of the 0.8% Pd/PdO- $\text{In}_2\text{O}_3$  sensor did not change significantly during the 11 consecutive cycle stability tests, the relative standard deviation (RSD) of its response value was 5.2%. Meanwhile, the changes in response/recovery time during 11 cycles were statistically analyzed (Fig. 8b), revealing that the response time remained relatively stable as the cycle number increased, while the recovery time showed an increasing trend, this may be related to the incomplete desorption of the material and the

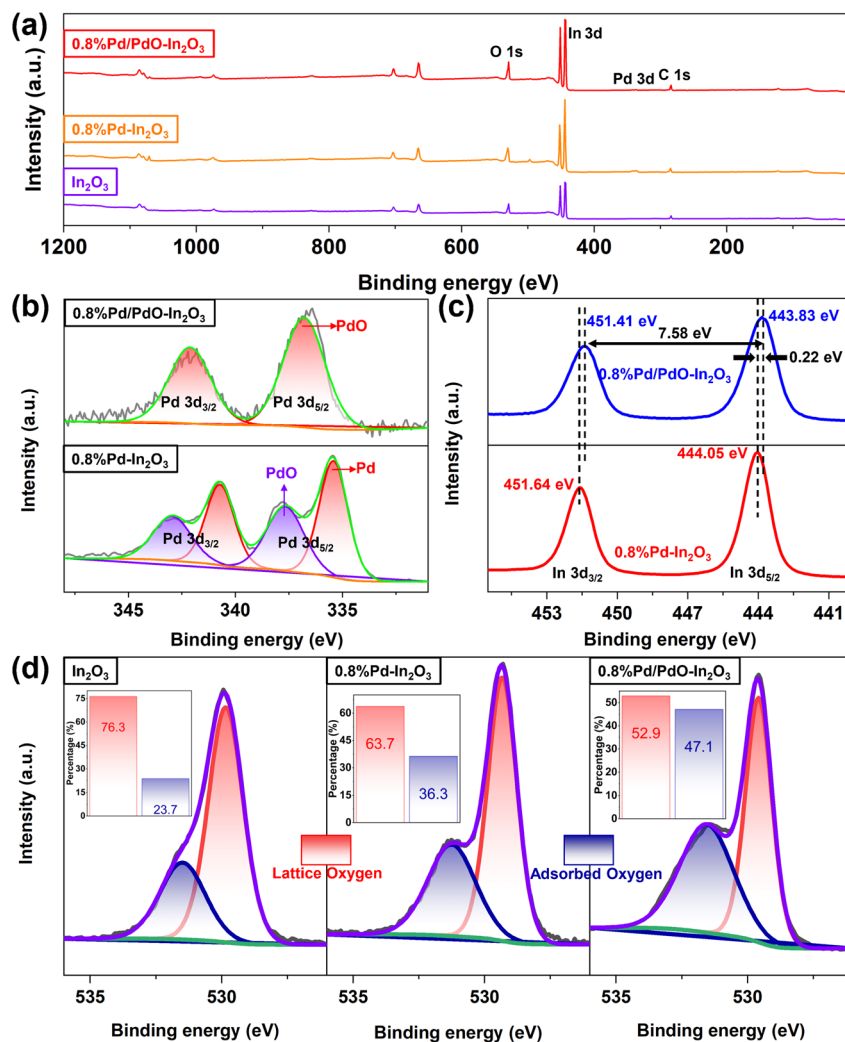


Fig. 6 (a) XPS full spectrum image of different samples, XPS high-resolution images of (b) Pd 3d, (c) In 3d and (d) O 1s.

decrease in desorption pathways caused by the increase in TEA concentration in the air. The selectivity of different sensors was also tested (Fig. 8c), it can be seen that the 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor has no obvious response to other common gases except formaldehyde and ammonia, indicating that its selectivity is better, in contrast, the selectivity of 0.8% Pd-In<sub>2</sub>O<sub>3</sub> and In<sub>2</sub>O<sub>3</sub> sensors was also tested, it can be seen that the surface modification of In<sub>2</sub>O<sub>3</sub> nanorods with Pd nanoparticles does not effectively improve its selectivity, both of them show relatively high sensitivity to TEA and ammonia.

The moisture resistance test is shown in Fig. 8d, in contrast to the sharp decrease in the response value of the In<sub>2</sub>O<sub>3</sub> and 0.8% Pd-In<sub>2</sub>O<sub>3</sub> sensor after relative humidity (RH) augmentation, although the 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor also showed a decrease in response value, however, it still had a high response of 828 to 10 ppm TEA at 88% RH. The reason for the decrease in the response value is related to the fact that water molecules occupy the active sites of the material, excessive water molecules compete with the adsorption of oxygen molecules on the active sites of the material, which weakens the oxygen adsorption capacity of the material and causes the air

resistance of the material to decrease,<sup>31</sup> similarly, when the gas-sensing reaction is in progress, water molecules will also compete with TEA molecules for active sites, in summary, the competition between water molecules and oxygen molecules/TEA molecules reduces the response value of the sensor. Different from some research that uses highly conductive materials to resist the impact of humidity,<sup>32,33</sup> in this study, the reason for the enhanced moisture resistance is related to the catalytic overflow effect of PdO, which increases the number of oxygen anions on the surface of In<sub>2</sub>O<sub>3</sub>,<sup>31</sup> which helps reduce the impact of water molecules.

In terms of long-term stability, a random long-term stability test was carried out on the 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor within 30 days (Fig. 8e). The results showed that the response value of the sensor did not drop/rise significantly, the long-term stability of the sensor has a response value RSD of 9.52%, showing a certain degree of fluctuation. The reason of fluctuation is mainly related to the humidity of the test environment, the slight variation in gas concentration during each test and the stability of the test equipment, the stability of the sensor can be improved by methods such as further modification to enhance

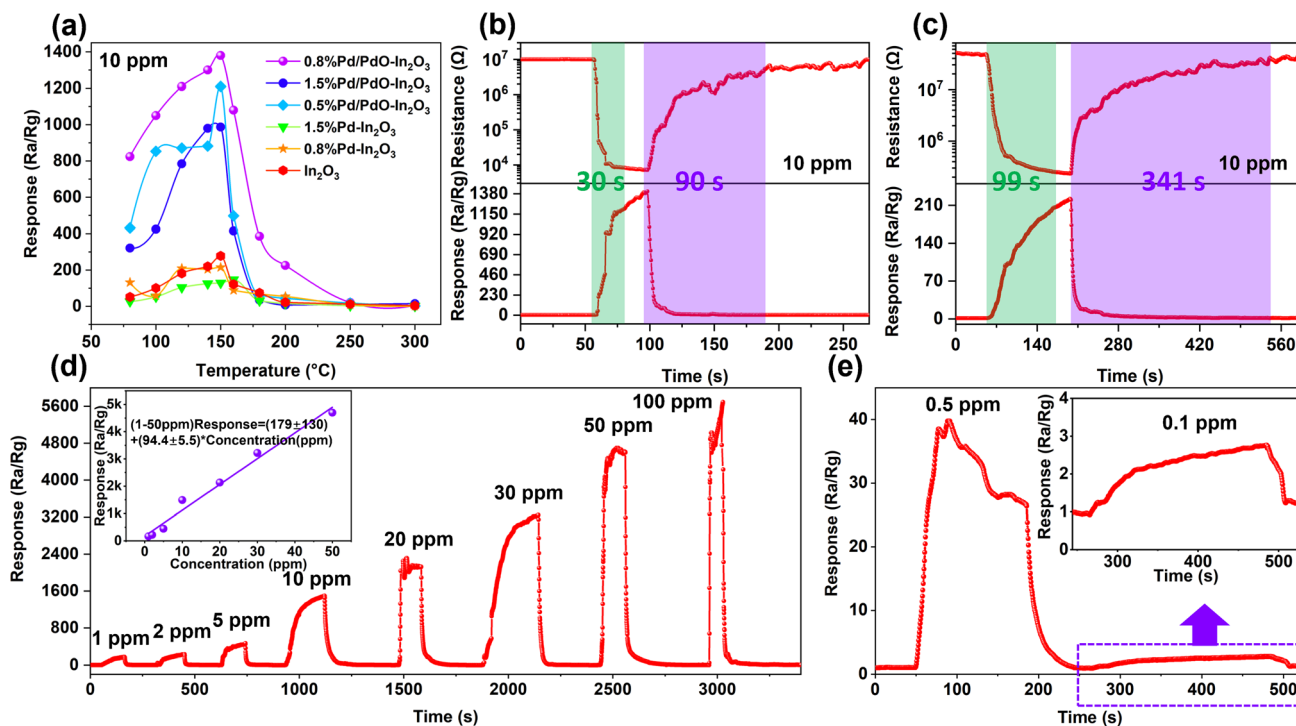


Fig. 7 Relative humidity: 45%, (a) the relationship between response values and operating temperature of different sensors, (b) transient resistance curve and response-time curve of 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor, (c) transient resistance curve and response-time curve of 0.8% Pd-In<sub>2</sub>O<sub>3</sub> sensor, (d) transient response curve of 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor to different TEA concentration (inset: linear fitting of sensor response values to 1–50 ppm TEA), (e) transient response curve of 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor to low concentration TEA.

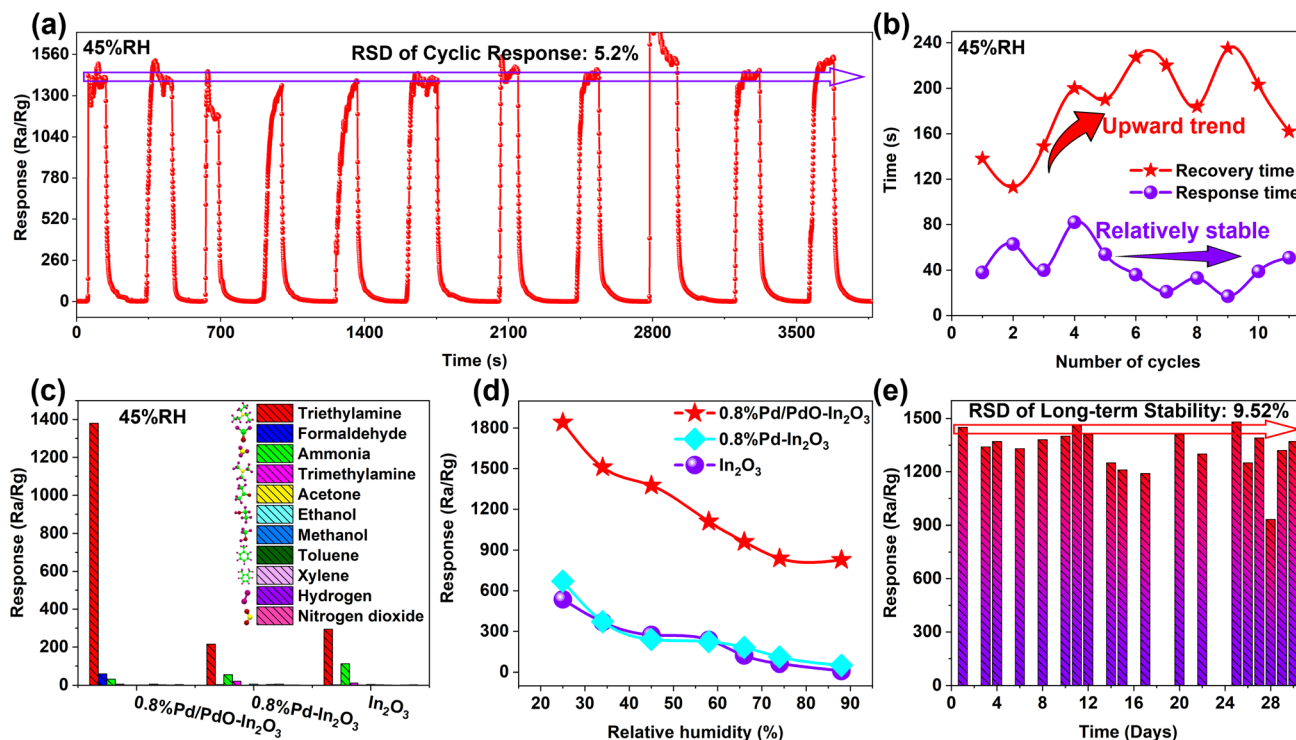


Fig. 8 Test environment: (10 ppm, 150 °C). (a) 11-cycle stability of 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor. (b) Statistical analysis of response–recovery time variation trend in cycles. (c) Selective testing of different sensors. (d) Humidity resistance test. (e) Long-term stability of 0.8% Pd/PdO-In<sub>2</sub>O<sub>3</sub> sensor.






the material's humidity resistance, establishing a humidity control group to reduce the response value variation caused by humidity, reducing gas concentration variation caused by human factors, using testing instruments with stable output signals, *etc.* Finally, the gas-sensing performance of recent related works are listed and shown in Table S2,<sup>†</sup> it can be seen that the results from this work are superior.

### Gas-sensing mechanism

It is well known that  $\text{In}_2\text{O}_3$  and PdO are typical metal oxide semiconductor (MOS) materials, and the most intuitive manifestation of their sensing performance is the change of their resistance. Simply put, the gas sensing process is the process of interaction between the sensing material and the target gas, this process will produce a series of chemical and physical changes, fully understanding this series of changes is of positive significance for the development of high-performance gas sensors. In the current study, the gas-sensing mechanism of MOS is usually explained using the adsorbed oxygen model and the EDL theory. In this study, when the gas-sensing reaction has not yet started, Pd/PdO- $\text{In}_2\text{O}_3$  exposed to the air will adsorb oxygen in the air, and consume electrons in its own conduction band to convert the adsorbed oxygen molecules into oxyanions (Fig. 9a and b), since in this study, the optimal operating temperature of the sensor is 150 °C, the oxyanion species at this time may be  $\text{O}_2^-/\text{O}^-$ ,<sup>34,35</sup> the oxygen adsorption process increases the thickness of the EDL of Pd/PdO- $\text{In}_2\text{O}_3$ , so the sensor at this time exhibits high resistance. When Pd/PdO- $\text{In}_2\text{O}_3$  is exposed to TEA

molecules (Fig. 9c), the adsorbed oxygen anions react with TEA molecules and return electrons to Pd/PdO- $\text{In}_2\text{O}_3$ , resulting in thinning of the EDL of Pd/PdO- $\text{In}_2\text{O}_3$ , this in turn reduces the resistance of the sensor. The process described above can be described by the following equation:



In this study, due to the introduction of Pd species, the gas sensing performance of Pd/PdO- $\text{In}_2\text{O}_3$  was significantly improved compared with the pristine  $\text{In}_2\text{O}_3$  sensor, and the improvement of Pd/PdO- $\text{In}_2\text{O}_3$  sensing performance was mainly due to the unique distribution of Pd species, electronic sensitization, and chemical sensitization are related.

As mentioned earlier, compared with Pd- $\text{In}_2\text{O}_3$ , the Pd species in Pd/PdO- $\text{In}_2\text{O}_3$  partly entered between  $\text{In}_2\text{O}_3$  nanoparticles and mainly existed in the form of PdO. Different from the surface modification effect of Pd nanoparticles distributed only on the surface of  $\text{In}_2\text{O}_3$ , this unique distribution enables the formation of multiple heterostructures between PdO and  $\text{In}_2\text{O}_3$  nanoparticles, this structure leads to an increase in the rate of electron transport and the number of electron transport channels in the material (Fig. 9b). At the same time, the unique distribution of PdO changes the distribution/accumulation of  $\text{In}_2\text{O}_3$  nanoparticles, which significantly increases the SSA of the

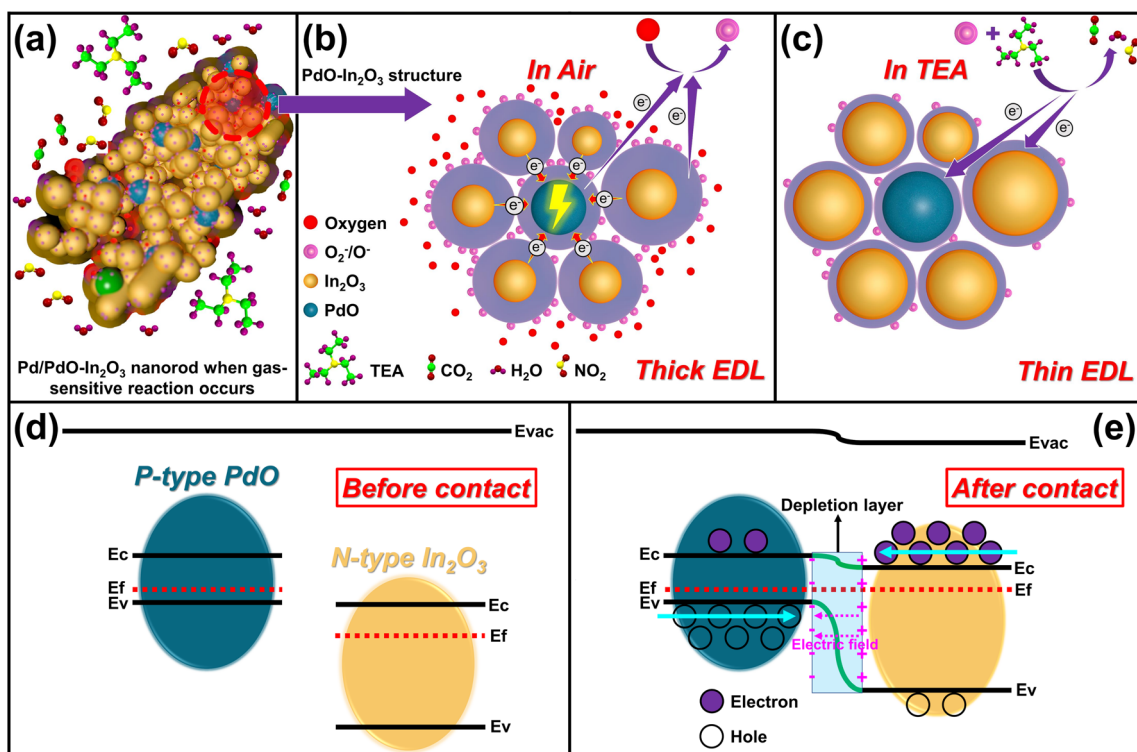


Fig. 9 (a) Schematic diagram of Pd/PdO- $\text{In}_2\text{O}_3$  during gas sensing reaction. Schematic diagram of gas sensing mechanism: (b) EDL in air, (c) EDL in TEA. (d) band structure of PdO and  $\text{In}_2\text{O}_3$  before contact. (e) band structure of PdO and  $\text{In}_2\text{O}_3$  after contact.

material, which is conducive to the attachment of more gases and participates in the gas-sensing reaction process, thus improving the gas-sensing performance.

Specifically, in terms of electronic sensitization, first of all, since PdO is a p-type semiconductor<sup>36</sup> and In<sub>2</sub>O<sub>3</sub> is an n-type semiconductor, a typical p–n heterojunction will be formed between them. Since the work function of PdO is higher than that of In<sub>2</sub>O<sub>3</sub> (ref. 37 and 38) (Fig. 9d), the electrons in the conduction band of In<sub>2</sub>O<sub>3</sub> will transfer to the work function of PdO, while the holes in the valence band of PdO will transfer to In<sub>2</sub>O<sub>3</sub>, which will eventually lead to the Fermi level balance of the two semiconductors,<sup>39</sup> due to the transfer of electrons, a wider EDL will be formed, and the energy band bending will occur at the contact interface between PdO and In<sub>2</sub>O<sub>3</sub> (Fig. 9e), and finally the air resistance ( $R_a$ ) of the material will increase significantly (Fig. S4†), since PdO exists as a small amount of modifier, Pd/PdO–In<sub>2</sub>O<sub>3</sub> behaves as an n-type semiconductor, so its response value is defined as  $R_a/R_g$  ( $R_g$  = gas resistance), electron sensitization mainly plays a role in increasing  $R_a$ .

Specifically, in terms of chemical sensitization, compared with pure In<sub>2</sub>O<sub>3</sub> nanorods, the heterojunction between PdO and In<sub>2</sub>O<sub>3</sub> forms a wider EDL, this is mainly the catalyst role of PdO to promote the transformation of oxygen molecules into O atoms (O<sub>2</sub>(gas) ↔ 2O(ads)), the increased oxygen atoms will partially spill over to the surface of In<sub>2</sub>O<sub>3</sub>, thus capturing electrons in the conduction band of In<sub>2</sub>O<sub>3</sub> to form oxygen anions, which ultimately leads to an increase in the amount of oxygen adsorbed by Pd/PdO–In<sub>2</sub>O<sub>3</sub>. Increased oxyanions mean that more oxygen species can be provided for the gas-sensing reaction, increasing the probability of TEA molecules interacting with oxyanions. Therefore, the chemosensitization effect accelerates the sensing reaction and improves the sensing performance.

## Conclusions

In conclusion, we successfully prepared Pd/PdO–In<sub>2</sub>O<sub>3</sub> nanorods with unique PdO distribution by precursor loading of Pd species and combined with subsequent calcination strategy. Which shows excellent sensing performance for TEA. The 0.8% Pd/PdO–In<sub>2</sub>O<sub>3</sub> sensor exhibited a high response of 1380 and a fast res/rec time of 30 s/90 s for 10 ppm TEA, and with good selectivity and stability at an optimal operating temperature of 150 °C, and a detection limit below 0.1 ppm. The gas sensing enhancement mechanism of PdO with unique distribution was further studied, the results show that the multiple heterojunctions formed between PdO particles and In<sub>2</sub>O<sub>3</sub> provide more electron transport channels and accelerate electron transport, this is the main reason why the 0.8% Pd/PdO–In<sub>2</sub>O<sub>3</sub> sensor has high response and fast res/rec characteristics. The Pd/PdO–In<sub>2</sub>O<sub>3</sub> sensor has a good application prospect in TEA detection because of its good sensing performance.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was funded by the National Key Research and Development Program of China (2022YFB3803600), the Key Research and Development Program of Yunnan Province (202302AF080002), Yunnan Yunling Scholars Project, Yunnan basic applied research project (202101AT070013), Young and middle-aged academic and technical leaders reserve talent project in Yunnan Province (202005AC160015). Authors thank the Electron Microscopy Center, the Advanced Computing Center, the Advanced Analysis and Measurement Center of Yunnan University for the sample testing and computations service.

## Notes and references

- 1 L. L. Guo, B. Zhang, X. L. Yang, S. S. Zhang, Y. Wang, G. D. Wang and Z. Y. Zhang, *Sens. Actuators, B*, 2021, **343**, 130126.
- 2 C. H. Hu, L. M. Yu, S. L. Li, M. L. Yin, H. B. Du and H. F. Li, *Sens. Actuators, B*, 2022, **355**, 131246.
- 3 B. Akesson, I. Floren and S. Skerfving, *Br. J. Ind. Med.*, 1985, **42**, 848–850.
- 4 B. Gandu, K. Sandhya, A. G. Rao and Y. V. Swamy, *Bioresour. Technol.*, 2013, **139**, 155–160.
- 5 Y. H. Zou, S. Chen, J. Sun, J. Q. Liu, Y. K. Che, X. H. Liu, J. Zhang and D. J. Yang, *ACS Sens.*, 2017, **2**, 897–902.
- 6 S. X. Shi, F. Zhang, H. M. Lin, Q. Wang, E. B. Shi and F. Y. Qu, *Sens. Actuators, B*, 2018, **262**, 739–749.
- 7 W. R. Li, H. Y. Xu, T. Zhai, H. Q. Yu, Q. Xu, X. P. Song, J. Q. Wang and B. Q. Cao, *J. Alloys Compd.*, 2017, **695**, 2930–2936.
- 8 Y. P. Wu, W. Zhou, W. W. Dong, J. Zhao, X. Q. Qiao, D. F. Hou, D. S. Li, Q. C. Zhang and P. Y. Feng, *Cryst. Growth Des.*, 2017, **17**, 2158–2165.
- 9 J. J. Liu, L. Y. Zhang, J. J. Fan and J. G. Yu, *Small*, 2022, **18**, 2104984.
- 10 W. Yang, L. Feng, S. H. He, L. Y. Liu and S. T. Liu, *ACS Appl. Mater. Interfaces*, 2018, **10**, 27131–27140.
- 11 L. L. Zheng, T. T. Ma, Y. Q. Zhao, Y. S. Xu, L. Sun, J. Zhang and X. H. Liu, *Sens. Actuators, B*, 2019, **290**, 155–162.
- 12 Q. Ma, S. S. Chu, H. Li, J. Guo, Q. Zhang and Z. Q. Lin, *Appl. Surf. Sci.*, 2021, **569**, 151074.
- 13 V. Subramanian, E. E. Wolf and P. V. Kamat, *J. Am. Chem. Soc.*, 2004, **126**, 4943–4950.
- 14 Y. Guo, B. H. Liu, Z. H. Duan, Z. Yuan, Y. D. Jiang and H. L. Tai, *Mater. Chem. Phys.*, 2023, **302**, 127768.
- 15 T. Tang, Z. Li, Y. F. Cheng, H. G. Xie, X. X. Wang, Y. L. Chen, L. Cheng, Y. Liang, X. Y. Hu, C. M. Hung, N. D. Hoa, H. Yu, B. Y. Zhang, K. Xu and J. Z. Ou, *J. Hazard. Mater.*, 2023, **451**, 131184.
- 16 X. Duan, Z. Duan, Y. Zhang, B. Liu, X. Li, Q. Zhao, Z. Yuan, Y. Jiang and H. Tai, *Sens. Actuators, B*, 2022, **369**, 132302.
- 17 X. J. Liu, K. R. Zhao, X. L. Sun, C. Zhang, X. P. Duan, P. Y. Hou, G. Zhao, S. W. Zhang, H. C. Yang, R. Y. Cao and X. J. Xu, *Sens. Actuators, B*, 2019, **285**, 1–10.

- 18 Y. Wang, H. S. Zhang and J. L. Cao, *Mater. Chem. Phys.*, 2022, **279**, 124749.
- 19 J. H. Lee, J. H. Kim, J. Y. Kim, A. Mirzaei, H. W. Kim and S. S. Kim, *Sensors*, 2019, **19**, 4276.
- 20 H. C. Ji, W. Zeng and Y. Q. Li, *Nanoscale*, 2019, **11**, 22664–22684.
- 21 Y. B. Luo, B. X. An, J. L. Bai, Y. R. Wang, X. Cheng, Q. Wang, J. P. Li, Y. F. Yang, Z. K. Wu and E. Q. Xie, *J. Colloid Interface Sci.*, 2021, **599**, 533–542.
- 22 R. Ahmad, S. M. Majhi, X. X. Zhang, T. M. Swager and K. N. Salama, *Adv. Colloid Interface Sci.*, 2019, **270**, 1–27.
- 23 F. B. Gu, M. Y. Di, D. M. Han, S. Hong and Z. H. Wang, *ACS Sens.*, 2020, **5**, 2611–2619.
- 24 P. Rai, J. W. Yoon, C. H. Kwak and J. H. Lee, *J. Mater. Chem. A*, 2016, **4**, 264–269.
- 25 H. Y. Lai and C. H. Chen, *J. Mater. Chem.*, 2012, **22**, 13204–13208.
- 26 X. X. Chang, T. Wang, P. Zhang, J. J. Zhang, A. Li and J. L. Gong, *J. Am. Chem. Soc.*, 2015, **137**, 8356–8359.
- 27 Z. J. Li, H. Li, Z. L. Wu, M. K. Wang, J. T. Luo, H. D. Torun, P. A. Hu, C. Yang, M. Grundmann, X. T. Liu and Y. Q. Fu, *Mater. Horiz.*, 2019, **6**, 470–506.
- 28 K. Zhang, S. W. Qin, P. G. Tang, Y. J. Feng and D. Q. Li, *J. Hazard. Mater.*, 2020, **391**, 122191.
- 29 Z. M. Deng, Y. M. Zhang, D. Xu, B. Y. Zi, J. Y. Zeng, Q. Lu, K. Xiong, J. Zhang, J. H. Zhao and Q. J. Liu, *ACS Sens.*, 2022, **7**, 2577–2588.
- 30 J. M. Walker, S. A. Akbar and P. A. Morris, *Sens. Actuators, B*, 2019, **286**, 624–640.
- 31 J. J. Liu, L. Y. Zhang, J. J. Fan, B. C. Zhu and J. G. Yu, *Sens. Actuators, B*, 2021, **331**, 129425.
- 32 Z. Yuan, Q. N. Zhao, Z. H. Duan, C. Y. Xie, X. H. Duan, S. R. Li, Z. B. Ye, Y. D. Jiang and H. L. Tai, *Sens. Actuators, B*, 2022, **363**, 131790.
- 33 T. Tang, Z. Li, Y. F. Cheng, K. Xu, H. G. Xie, X. X. Wang, X. Y. Hu, H. Yu, B. Y. Zhang, X. W. Tao, C. M. Hung, N. D. Hoa, G. Y. Chen, Y. X. Li and J. Z. Ou, *J. Mater. Chem.*, 2023, **11**, 6361–6374.
- 34 S. M. Majhi, H. J. Lee, H. N. Choi, H. Y. Cho, J. S. Kim, C. R. Lee and Y. T. Yu, *Crystengcomm*, 2019, **21**, 5084–5094.
- 35 N. Barsan and U. Weimar, *J. Electroceram.*, 2001, **7**, 143–167.
- 36 S. R. Wang, Y. J. Wang, J. Q. Jiang, R. Liu, M. Y. Li, Y. M. Wang, Y. Su, B. L. Zhu, S. M. Zhang, W. P. Huang and S. H. Wu, *Catal. Commun.*, 2009, **10**, 640–644.
- 37 Q. Li, W. Liang and J. K. Shang, *Appl. Phys. Lett.*, 2007, **90**, 063109.
- 38 M. H. Dun, M. H. Tang, D. Y. Zhao, X. H. Li and X. T. Huang, *Sens. Actuators, B*, 2022, **358**, 131520.
- 39 Y. Liu, S. T. Yao, Q. Y. Yang, P. Sun, Y. Gao, X. S. Liang, F. M. Liu and G. Y. Lu, *RSC Adv.*, 2015, **5**, 52252–52258.