



Cite this: *Phys. Chem. Chem. Phys.*, 2024, 26, 4579

# A first-principles study of electro-catalytic reduction of CO<sub>2</sub> on transition metal-doped stanene†

Sudatta Giri,<sup>a</sup> Satyesh K. Yadav <sup>b</sup> and Debolina Misra <sup>\*a</sup>

Employing first-principles calculations based on density functional theory, this work examines the activity of 3d transition metal-doped stanene for electro-catalytic CO<sub>2</sub> reduction through the first two electron transfer steps to CO. Our results related to CO<sub>2</sub> activation, the first and a crucial step of the reduction process revealed that, among the entire 3d transition metal row studied, only Ti- and Fe-doped stanene can bind and significantly activate the CO<sub>2</sub> molecule, while the rest of the TM single atoms are inert in activating the molecule. The activation of the CO<sub>2</sub> molecule on Ti- and Fe-doped stanene has been observed in the presence of water as well. In addition, the formation of OCHO has been observed to be energetically preferred over COOH formation as a reaction intermediate, indicating the preference for the formate path of the reduction reaction. Furthermore, despite the strong adsorption of H<sub>2</sub>O on the catalyst surface, the presence of water seems to enhance CO<sub>2</sub> adsorption on the catalysts, contrary to what has been observed recently in graphene-based catalysts. Finally, our difference charge density and the Bader charge calculations reveal that the ability of Ti- and Fe-doped stanene in activating the CO<sub>2</sub> molecule and their potential catalytic activity for CO<sub>2</sub> reduction is to be attributed to the charge transfer between the catalyst and the molecule, providing new insights into the rational design of 2D catalysts beyond graphene.

Received 6th October 2023,  
Accepted 3rd January 2024

DOI: 10.1039/d3cp04841a

[rsc.li/pccp](http://rsc.li/pccp)

## 1 Introduction

Electrochemical conversion of CO<sub>2</sub> into value added products has emerged as a sustainable way to alleviate global warming, and as a promising solution to address the current energy crisis.<sup>1–6</sup> The advantage of the electro-catalytic CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR) lies in the fact that the reaction can proceed under ambient conditions on efficient electrocatalysts,<sup>7–20</sup> and can be controlled by suitably changing the applied potential.<sup>21</sup> Reduction of CO<sub>2</sub> to CO is considered as the first step of this process<sup>22</sup> and is highly important for the chemical industry.<sup>23</sup> Nevertheless, the major bottleneck even for this two electron reduction reaction,<sup>22</sup> is due to the poor selectivity, compromised stability, high cost and low transformation efficiency of the conventional catalysts.<sup>24–28</sup> Design and development of non-precious and highly active catalysts with better selectivity and stability is hence highly necessary. Recently, two-dimensional (2D) nano-materials have drawn immense attention due to their unique

structural and electronic properties, high surface to volume ratio and higher maneuverability compared to their bulk counterparts,<sup>14,29–33</sup> enabling their potential usage in an extensive range of applications. Lately, stanene, among the recently developed group iv monolayers, has exhibited efficiency for sensing triatomic gases such as CO<sub>2</sub>, NO<sub>2</sub> and SO<sub>2</sub><sup>34–40</sup> and its ability to attain higher room temperature conductivity compared to graphene and silicene through efficient doping.<sup>39</sup> In spite of the unique structural and electronic properties of stanene and its already proven ability to capture and sense CO<sub>2</sub> gas, the role of stanene as a catalyst for the CO<sub>2</sub>RR is not yet explored thoroughly. Employing first-principles calculations based on density functional theory (DFT), this work intends to investigate the activity of pure and 3d transition metal (TM: Sc to Zn)-doped stanene towards CO<sub>2</sub> reduction.

This article is structured as follows: Section 2 provides the computational details. In Section 3 we discuss our results involving both pure and 3d TM-doped stanene as catalysts for the reduction of CO<sub>2</sub> to CO, and Section 4 provides the conclusion.

## 2 Computational details

Spin polarized density functional theory calculations have been performed using the Vienna ab initio simulation package (VASP)<sup>41</sup> employing the projected augmented wave (PAW)

<sup>a</sup> Materials Modelling and Simulation Laboratory, Department of Physics, Indian Institute of Information Technology, Design and Manufacturing, Kancheepuram, Chennai, 600127, India. E-mail: [debolinam@iiitdm.ac.in](mailto:debolinam@iiitdm.ac.in)

<sup>b</sup> Department of Metallurgical and Materials Engineering, Indian Institute of Technology Madras, 600036, India

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3cp04841a>

method<sup>42</sup> and a plane wave basis<sup>43</sup> set. The generalized gradient approximation (GGA) as implemented in the Perdew–Burke–Ernzerhof (PBE)<sup>44</sup> functional has been employed and D3 Grimme-dispersion correction<sup>45</sup> to address the van der Waals interaction is incorporated in all our calculations. The total energy of the stanene layer per atom is calculated as  $-3.48$  eV per atom,  $0.09$  eV less than the energy reported using the HSE06 functional.<sup>46</sup> A fully optimized unit cell of stanene has  $a = b = 4.67$  Å, a Sn–Sn bond length of  $2.83$  Å, and a buckling height of  $0.86$  Å. The calculated values are all within a reasonable agreement with previous reports.<sup>40,47–50</sup> A  $4 \times 4$  supercell constructed from the unit cell with  $20$  Å vacuum introduced along the  $z$  direction was further used to construct doped stanene structures. TM single atom (SA)-doped stanene with a doping concentration of  $3.12\%$  is depicted in Fig. 1a. All the structures are optimized using the conjugate gradient scheme with a  $5 \times 5 \times 1$  Monkhorst–Pack<sup>51</sup>  $k$ -mesh and a plane wave energy cut-off of  $450$  eV. The calculations are considered converged when the energy difference between successive iterations becomes less than  $10^{-5}$  eV and the force exerted on each atom is less than  $0.001$  eV Å<sup>-1</sup>. The stability of a TM single atom in stanene is calculated from its binding energy (B.E.) calculated as,

$$\text{B.E.} = E_{\text{TM@Stanene}} - E_{\text{Stanene}} - E_{\text{TM}}$$

where  $E_{\text{TM@Stanene}}$ ,  $E_{\text{TM}}$  and  $E_{\text{Stanene}}$  are the energies of TM doped stanene, of a single TM atom, and of the energy of the pristine stanene monolayer, respectively. The adsorption energy ( $E_{\text{ads}}$ ) of a molecule adsorbed on the catalyst has been computed using the following equation,<sup>52</sup>

$$E_{\text{ads}} = E_{\text{cat+mol}} - E_{\text{cat}} - E_{\text{mol}}$$

$E_{\text{cat+mol}}$ ,  $E_{\text{cat}}$  and  $E_{\text{mol}}$  are the energies of the catalyst with the adsorbed molecule, of the catalyst and of the isolated molecule, respectively.

The reaction free energy change  $\Delta G$  is calculated as  $\Delta G = \sum G(\text{products}) - \sum G(\text{reactants})$  where the free energy for each adsorbed species is calculated using the following equation,<sup>53</sup>

$$G = E_{\text{DFT}} - TS + \text{ZPE}$$

Here,  $E_{\text{DFT}}$  is the DFT calculated electronic energy,<sup>54</sup>  $S$  and  $\text{ZPE}$  are the entropy and zero-point energy correction, respectively,

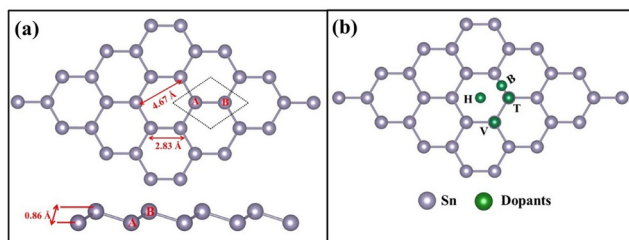


Fig. 1 (a) Top and side view of an optimized  $4 \times 4$  stanene supercell. The dotted area indicates a single unit cell. The buckling height of  $0.86$  Å is the distance observed between the A and B sublattices. (b) Possible sites to add the TM dopants.

and the corresponding values for the reaction intermediates are taken from the literature.<sup>52,55</sup> For all the proton coupled electron transfer (PCET) steps of the  $\text{CO}_2\text{RR}$ , the chemical potential of a proton and electron pair is considered as  $\frac{1}{2}$  of the chemical potential of gaseous hydrogen, as per the CHE model.<sup>54</sup> The limiting potential ( $U_L$ ) is determined as,<sup>56</sup>

$$U_L = -\Delta G_{\text{max}}/e$$

where  $e$  is electronic charge and  $\Delta G_{\text{max}}$  is the highest change in free energy observed in the potential limiting step (PLS) of the reaction.

## 3 Results and discussion

### 3.1 The binding sites for TM in stanene

Four possible binding sites, namely (i) hollow (H): center of hexagon, (ii) top (T): top of an Sn atom in the upper sublattice, (iii) valley (V): top of an Sn atom in the lower sublattice, and (iv) bridge site (B): in between two adjacent Sn atoms,<sup>48</sup> were investigated to find the most preferred binding position for the TM atoms (Sc to Zn) doped in stanene (Fig. 1b). The binding energy (B.E.) value for each TM dopant in stanene is listed in Table 1.

Table 1 shows that the hollow site (H) is the most preferred binding site for all TM atoms studied, except Co and Zn. For Co and Zn, the valley site (V) is the preferred site for TM binding. It has also been observed that the bridge site is unstable for all TM atoms, except Zn. For Zn, however, the difference in binding energies between the valley and bridge sites is very small ( $0.02$  eV). For other TM atoms, our simulations revealed that if doped at the bridge site, the TM atom will eventually migrate to the valley site. It has also been noticed that, TM atoms, when added at the valley site, move closer to the plane of the stanene monolayer and push the Sn atom slightly away from the plane. The negative binding energies indicate the strong binding of TM-SACs on stanene.<sup>57,58</sup> Fig. 2 depicts the TM single atoms at the most preferred doping sites in stanene.

From our calculations it is evident that, the TM binding energy is stronger for the early transition metals (Sc to V), with Ti, which shares the same number of valence electrons as Sn, exhibiting the highest binding energy amongst all the TMs studied. The binding energy, however, decreases in Cr and Mn

Table 1 Binding energies of 3d TM atoms on all four possible doping sites

TM	B.E. (eV)			
	Top (T)	Hollow (H)	Valley (V)	Bridge (B)
Sc	-3.28	-3.99	-3.74	Unstable
Ti	-2.10	-4.33	-3.90	Unstable
V	-2.72	-3.58	-3.11	Unstable
Cr	-1.11	-2.33	-1.94	Unstable
Mn	-1.11	-2.38	-2.19	Unstable
Fe	-1.37	-3.14	-3.05	Unstable
Co	-3.25	-3.52	-3.56	Unstable
Ni	-3.32	-3.78	-3.64	Unstable
Cu	-1.57	-2.57	-2.39	Unstable
Zn	-0.41	0.10	-0.44	-0.42

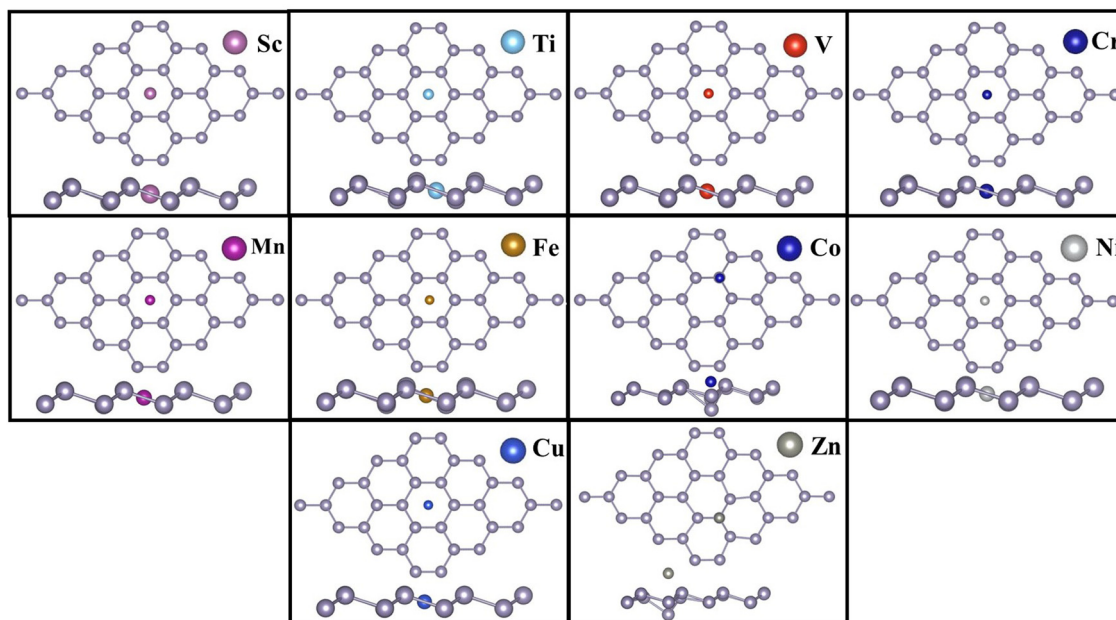


Fig. 2 TM SAs at their preferred doping sites in stanene.

Table 2 TM–Sn distance ( $d_{\text{TM-Sn}}$ ), Sn–Sn distance ( $d_{\text{Sn-Sn}}$ ), and magnetization for TM, doped at the most preferred binding site in stanene

TM	$d_{\text{TM-Sn}}$ (Å)	$d_{\text{Sn-Sn}}$ (Å)	$\mu_{\text{d}}$
Sc	2.88	3.03	0.00
Ti	2.80	3.03	0.84
V	2.80	2.95	2.40
Cr	2.82	2.92	3.64
Mn	2.80	2.94	3.71
Fe	2.73	2.92	2.60
Co	2.43	3.29	1.46
Ni	2.72	2.85	0.00
Cu	2.77	2.89	0.00
Zn	4.01	2.91	0.00

where both the TMs possess a half-filled 3d shell. The B.E. increases again for Fe, Co and Ni, and decreases in late TMs Cu and Zn. The structural geometries of the TM embedded stanene layer and the corresponding TM magnetizations are listed in Table 2. It is apparent that incorporation of the TM SA in stanene results in local distortion with the maximum distortion observed in Co-doped stanene, where the Co atom pushes the Sn atom away from the plane towards the valley site and the local Sn–Sn bond length stretches to 3.29 Å. For the other TMs, the Sn–Sn bond length varies from 2.85 Å in Ni-, to 3.03 Å in Sc-doped stanene. While most of the TM SAs exhibit strong chemisorption with the stanene sheet, with the TM–Sn distance varying from 2.43 Å to 2.88 Å, for Zn, physisorption is observed with a Zn–Sn distance of 4.01 Å and a binding energy of  $-0.44$  eV. The weak binding of Zn in stanene compared to other TMs can be attributed to its closed shell structure.

### 3.2 CO<sub>2</sub> reduction to CO on bare catalysts

**3.2.1 CO<sub>2</sub> activation.** CO<sub>2</sub> activation is the first and a crucial step of CO<sub>2</sub>RR, although largely ignored in most of the

Table 3 TM–C distance, O–C–O angle, adsorption energies ( $E_{\text{ads}}$ ) and free energies ( $\Delta G$ ) for CO<sub>2</sub> adsorption. TM magnetization is also listed

TM	$d_{\text{TM-C}}$ (Å)	$\angle$ O–C–O	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)	$\mu_{\text{d}}$
Pure stanene	3.64	179.7	$-0.09$	0.59	0.00
TM@Sn					
Sc	4.61	179.7	$-0.29$	0.39	0.00
Ti	2.23	149.4	0.09	0.77	0.60
V	4.16	179.6	$-0.16$	0.52	2.38
Cr	4.49	179.9	$-0.21$	0.47	3.76
Mn	4.41	179.9	$-0.19$	0.49	3.67
Fe	2.06	148.4	$-0.12$	0.56	0.84
Co	3.44	179.6	$-0.11$	0.57	1.40
Ni	3.53	179.1	$-0.27$	0.41	0.00
Cu	4.03	179.7	$-0.14$	0.54	$-0.02$
Zn	3.41	179.6	$-0.15$	0.53	0.00

studies pertaining to CO<sub>2</sub>RR.<sup>59–63</sup> Thus, as a first step to understand the CO<sub>2</sub>RR on TM@Sn, we analysed the efficiency of the TM SAs to bend and therefore to activate the CO<sub>2</sub> molecule. The structural geometry of the complex, the adsorption energies and the reaction free energies of the CO<sub>2</sub> molecule, and the TM magnetization after CO<sub>2</sub> adsorption are listed in Table 3.

For CO<sub>2</sub> adsorption on pristine stanene (Fig. 3a), a weak physisorption ( $E_{\text{ads}} -0.09$  eV) is observed with no activation of the molecule. Our simulations for the entire 3d TM row studied revealed that, only Ti and Fe can activate the CO<sub>2</sub> molecule. For Ti, the CO<sub>2</sub> molecule is activated with  $\angle$  O–C–O of 149°, and the C–O bond is elongated to 1.22 Å. For Fe, the activation of the CO<sub>2</sub> molecule is observed with  $\angle$  O–C–O reducing to 148° and the bond length is increased to 1.22 Å. For the rest of the TM SAs, no activation of the CO<sub>2</sub> molecule is observed. For Sc@Sn, the Sn atom is pushed slightly out of the plane of the stanene monolayer and the CO<sub>2</sub> molecule moves further away from the

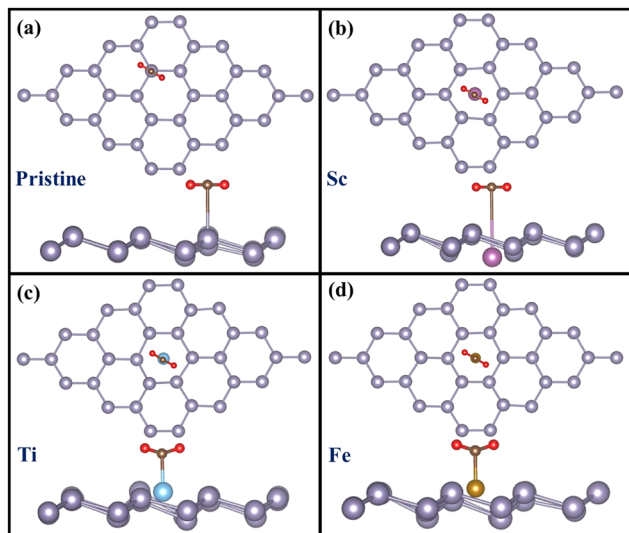


Fig. 3 CO<sub>2</sub> adsorption on (a) pristine, (b) Sc-, (c) Ti- and (d) Fe-doped stanene monolayers: top view and side view.





plane. The same trend has been observed for other TMs (V, Cr, Mn, Co and Cu) with no activation of the CO<sub>2</sub> molecule. For Ni@Sn as well, no activation in CO<sub>2</sub> is observed, and our calculated CO<sub>2</sub> adsorption energy of  $-0.27$  eV is consistent with previous reports involving Ni SAC in similar materials.<sup>64</sup>

Henceforth, we focus our attention on Ti and Fe-doped stanene as they activate the CO<sub>2</sub> molecule and hence are likely to be active in the CO<sub>2</sub>RR. In addition, Sc-doped stanene is also studied for comparison, Sc being the representative of the TMs that does not activate the CO<sub>2</sub> molecule. The optimized geometries of CO<sub>2</sub> adsorption on TM@Sn (Sc, Ti and Fe) are shown in Fig. 3.

Our *ab initio* molecular dynamics (AIMD) simulation at 300 K for 5 ps verifies the kinetic stability of the catalysts that activate CO<sub>2</sub>. As depicted in Fig. S1 (ESI<sup>†</sup>), the energy and temperature profiles of Ti- and Fe-doped stanene oscillate within a very small range, indicating the stability of these catalytic systems. Additionally, the thermodynamic and electrochemical stability of the catalysts have also been investigated (ESI<sup>†</sup>). Our calculated formation energy per unit area for pure stanene within the GGA-PBE framework is  $-0.26$  eV Å<sup>-2</sup> with a deviation of  $+0.09$  eV Å<sup>-2</sup> from the HSE06 value of  $-0.35$  eV Å<sup>-2</sup> reported earlier.<sup>46</sup> The stability further increases in TM-doped stanene with the order  $\Delta E_{\text{Ti@Sn}} < \Delta E_{\text{Fe@Sn}} < \Delta E_{\text{Sn}}$  (Table S2, ESI<sup>†</sup>). Furthermore, our dissolution potential calculations for the catalysts (Table S2, ESI<sup>†</sup>) indicate the electrochemical stability of TM@Sn as well. Our results are in range with the existing reports on similar 2D materials<sup>65</sup> and the absolute deviations from the reported values for a specific TM are attributed to the different levels of theory involved in the respective work.

**3.2.2 Reaction intermediates.** CO<sub>2</sub>RR is an intricate process involving multiple proton-electron transfer steps, and various reaction intermediates. The pathway involving a two-electron transfer mechanism is explored in our study (reduction of CO<sub>2</sub>

to CO) and the subsequent equations describing the possible intermediates for the same are given below.<sup>66</sup>



where the catalyst is indicated by an asterisk and the asterisk placed prior to an adsorbate signifies its binding on the catalyst.

The subsequent step after CO<sub>2</sub> activation entails the first hydrogenation process, leading to the formation of COOH or OCHO. This step holds substantial significance as it plays a crucial role in determining both the end products and the desired reaction pathway, as the formation of COOH (OCHO) indicates the preference for the carboxylic (formate) pathway.<sup>52,67</sup> Hence in our study following the CO<sub>2</sub> activation over Ti and Fe doped stanene, we compared the probabilities of formation of both COOH and OCHO as reaction intermediates. For Ti@Sn, our calculation revealed that OCHO formation has higher energy preference ( $\Delta G = -1.51$  eV) over COOH ( $\Delta G = -0.70$  eV). Subsequently, the next step of the reaction process, the formation of the intermediate HCOOH, has also been studied and the additional energy input required for the conversion of OCHO to HCOOH is calculated to be 1.37 eV. Interestingly, had COOH been the favored intermediate in the 1st hydrogenation step, the further conversion of COOH to CO would be an exothermic process with a free energy change of  $-0.38$  eV. The energy preference of OCHO over COOH has also been observed in previous reports.<sup>52,68</sup>

For Fe@Sn, we found a similar trend, where OCHO emerges as the energetically preferred intermediate in the 1st hydrogenation step over COOH ( $\Delta G = -0.88$  eV and 0.16 eV respectively). For the next step of the reaction, an energy input of 1.32 eV is required for HCOOH formation from OCHO. Similar to Ti@Sn, had COOH been the preferred intermediate in the initial step, the subsequent CO formation would have a free energy change of  $-1.17$  eV.

Hence, for both Ti- and Fe-doped Sn, OCHO to HCOOH formation is the potential limiting step (PLS), with the limiting potentials ( $U_L$ ) being  $-1.37$  V and  $-1.32$  V respectively. Fig. 4(a) and (b) display the optimal geometries and the corresponding free energy diagrams along the carboxylic and formate pathways for both the catalysts. For each reaction step the change in  $\Delta G$  as shown in Fig. 4(b) is considered with respect to the previous reaction step.<sup>69-71</sup> All the energy parameters are summarized in Table 4.

However, apart from the reaction intermediates mentioned above, H\* may also emerge as a part of the hydrogen evolution reaction (HER) that can occur simultaneously with CO<sub>2</sub>RR.<sup>72</sup> Hence, free energy changes related to H\* adsorption on the catalysts have been calculated and compared with that of COOH and OCHO, reaction intermediates from the 1st hydrogenation

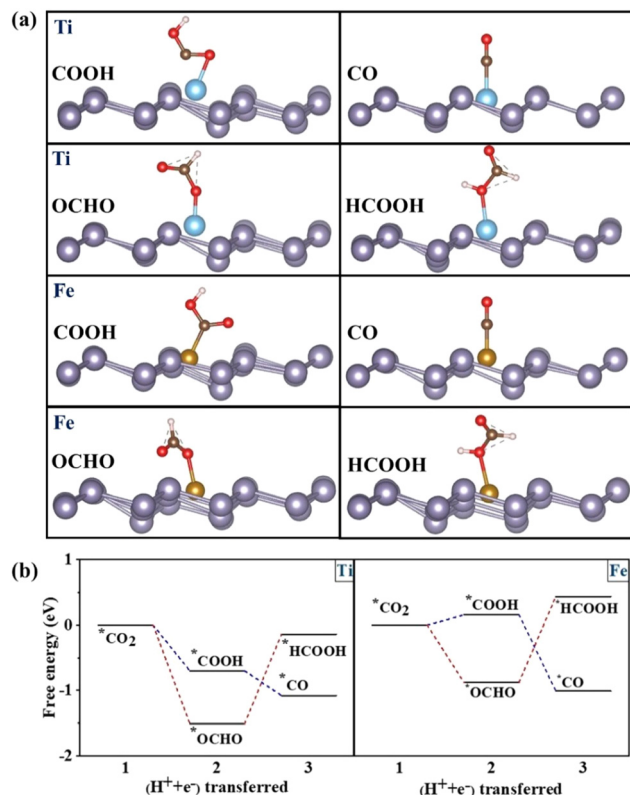


Fig. 4 (a) Optimized structures and (b) free energy profiles along the carboxylic and formate pathways for Ti- and Fe-doped stanene.

step of CO<sub>2</sub>RR.<sup>72</sup> The free energy change ( $\Delta G^H$ ) related to H-adsorption along the reaction pathway of HER came out to be  $-0.09$  eV and  $0.16$  eV for Ti- and Fe doped stanene, respectively. Hence, we found that  $\Delta G^{\text{OCHO}} < \Delta G^{\text{COOH}} < \Delta G^H$  for Ti-doped stanene, and  $\Delta G^{\text{OCHO}} < \Delta G^{\text{COOH}} = \Delta G^H$  for Fe@Sn. The lowest Gibbs free energy change has been observed for OCHO formation in both the cases, indicating that the formation of OCHO is most preferred among all the reactants considered, and the catalysts are selective towards CO<sub>2</sub>RR over HER.<sup>72</sup>

### 3.3 CO<sub>2</sub> reduction in water

As CO<sub>2</sub>RR occurs in aqueous medium, CO<sub>2</sub> activation in the presence of water has also been studied for these systems. However, in order to understand CO<sub>2</sub> adsorption on wet catalysts, first the catalysts' ability to bind water molecules has been investigated.

**3.3.1 H<sub>2</sub>O adsorption on TM@Sn.** The optimized catalyst structures with adsorbed H<sub>2</sub>O are shown in Fig. 5 and the adsorption energies and the structural geometries are listed in Table 5.

It is apparent that H<sub>2</sub>O binds weakly on pure and Zn-doped stanene with  $E_{\text{ads}}$  of  $-0.16$  eV and  $-0.12$  eV, respectively. However, in all the TM-doped stanenes (except Zn), water binds strongly on the catalyst with the strongest adsorption observed in Sc-doped stanene ( $-1.18$  eV). To explore the effect of water on CO<sub>2</sub> binding and activation on the catalyst, we further studied CO<sub>2</sub> adsorption on TM@Sn in the presence of a water molecule as described below.

**3.3.2 Co-adsorption of CO<sub>2</sub> and H<sub>2</sub>O on TM@Sn.** For simulating adsorption of CO<sub>2</sub> in the presence of H<sub>2</sub>O, the 2D symmetry of the catalyst can be exploited considering CO<sub>2</sub> and H<sub>2</sub>O located on the same side as well as on the opposite sides of the stanene monolayer.<sup>52</sup> In the present study, we have considered adsorption of one H<sub>2</sub>O molecule (i) on the same side and (ii) on the opposite side of CO<sub>2</sub> on the catalyst. The detailed structural geometry, the adsorption energies ( $E_{\text{ads}}$ ) and the adsorption free energies for co-adsorption of CO<sub>2</sub> and H<sub>2</sub>O are listed in Table 6. The adsorption energies for CO<sub>2</sub> are calculated considering the catalyst with pre-adsorbed H<sub>2</sub>O as a reference. For CO<sub>2</sub> and H<sub>2</sub>O adsorption on the opposite sides, both the molecules move away from a pure stanene monolayer with no activation of the CO<sub>2</sub> molecule. In Sc-doped stanene, the Sc atom moves closer to the H<sub>2</sub>O molecule, in line with its ability to bind H<sub>2</sub>O strongly. Furthermore, similar to dry Sc@Sn, there is no activation of CO<sub>2</sub> in the presence of H<sub>2</sub>O. A similar trend is observed when both the molecules lie on the same side of the Sc-doped stanene: the CO<sub>2</sub> and H<sub>2</sub>O molecules move away from each other and there is no activation of CO<sub>2</sub>. For Ti-doped stanene as well, the Ti atom moves very close to the H<sub>2</sub>O molecule as expected from its strong adsorption of H<sub>2</sub>O. We observe that the CO<sub>2</sub> molecule does not get activated when H<sub>2</sub>O is added on the opposite side of the catalyst. However, when adsorbed on the same side of the catalyst, the Ti atom moves closer to the CO<sub>2</sub> molecule and the latter gets activated on the catalyst with an adsorption energy of  $-0.39$  eV. In Fe-doped stanene, on the other hand, CO<sub>2</sub> gets activated in both cases and the H<sub>2</sub>O molecule moves away from the Fe atom. A strong binding and subsequent activation of CO<sub>2</sub> is evident from the O-C-O bond angle of  $149^\circ$  ( $141^\circ$ ) and an elongated C-O bond of  $1.22$  Å ( $1.29$  Å) when placed on the opposite (same) side of H<sub>2</sub>O on Fe-doped stanene.

Our calculations revealed that the catalysts that activated CO<sub>2</sub> in the dry phase also activate the molecule in the presence of water. Surprisingly, the presence of water in close vicinity seems to enhance the strength of CO<sub>2</sub> adsorption on the catalyst: and the adsorption energy decreases by  $0.48$  and  $0.16$  eV for Ti and Fe, respectively, a behaviour opposite to what has recently been observed in N-doped graphene.<sup>52</sup>

Table 4 Change in free energy along the reaction pathway and limiting potentials for Ti- and Fe-doped stanene

TM	COOH		CO		OCHO		HCOOH		PLS	$U_L$ (V)
	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)		
Ti	$-3.09$	$-0.70$	$-1.85$	$-0.38$	$-4.04$	$-1.51$	$-0.73$	$1.37$	$^*\text{OCHO} + \text{H}^+ + \text{e}^- \rightarrow ^*\text{HCOOH}$	$-1.37$
Fe	$-2.45$	$0.16$	$-2.00$	$-1.17$	$-3.62$	$-0.88$	$-0.36$	$1.32$	$^*\text{OCHO} + \text{H}^+ + \text{e}^- \rightarrow ^*\text{HCOOH}$	$-1.32$

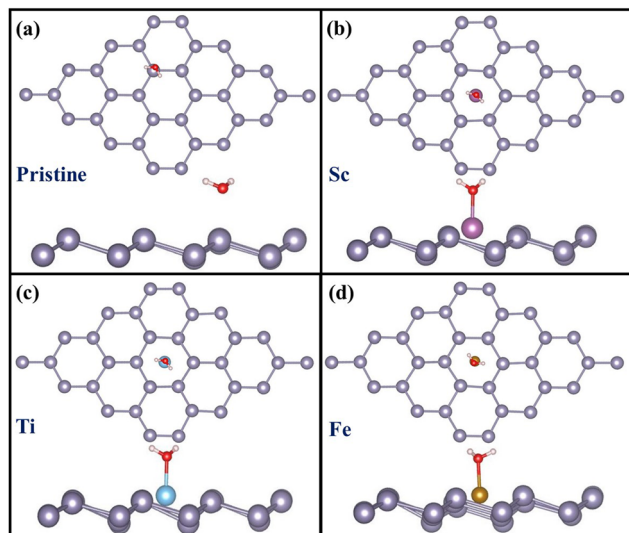


Fig. 5 H<sub>2</sub>O adsorption on (a) pristine and (b) Sc- (c) Ti- and (d) Fe-doped stanene: top view and side view.

Table 5 TM–O distance, H–O–H angle, adsorption energies ( $E_{\text{ads}}$ ) and free energies ( $\Delta G$ ) for H<sub>2</sub>O adsorption on TM@Sn. TM magnetization is also listed

	$d_{\text{TM-O}}$ (Å)	$\angle \text{H-O-H}$	$E_{\text{ads}}$ (eV)	$\Delta G$ (eV)	$\mu_{\text{d}}$
Pure stanene	2.95	105.0	−0.16	0.43	0.00
TM@Sn					
Sc	2.22	108.3	−1.18	−0.59	0.07
Ti	2.16	108.0	−0.96	−0.37	0.00
V	2.14	107.1	−0.69	−0.10	0.57
Cr	2.21	106.9	−0.67	−0.08	3.73
Mn	2.20	106.6	−0.72	−0.13	3.73
Fe	2.17	106.8	−0.61	−0.02	2.80
Co	2.10	106.8	−0.58	0.01	1.47
Ni	2.15	106.1	−0.50	0.09	0.00
Cu	2.22	106.0	−0.45	0.14	0.02
Zn	2.76	105.7	−0.12	0.47	0.00

To explore the origin of the enhanced CO<sub>2</sub> adsorption on the catalysts in the presence of water, the interaction energies between activated CO<sub>2</sub> and the nearby H<sub>2</sub>O molecules have been calculated as per the super-molecular approach.<sup>73,74</sup> The negative interaction energies resulted for Ti and Fe-doped stanene (ESI<sup>†</sup>) indicate the formation of H-bonds between the molecules. The H-bond lengths for Ti@Sn and Fe@Sn are 1.89 and 1.95 Å, respectively, similar to the H-bond lengths reported previously for various oxygen containing functional groups.<sup>75</sup> In addition, the distances between the donor and

acceptor atoms in Ti@Sn and Fe@Sn are much shorter than the sum of van der Waals radii of the donor and acceptor atoms and the O–H bond length in H<sub>2</sub>O (ESI<sup>†</sup>). Furthermore, our Bader charge analysis indicates the shift in electron density: charge on the O atom of water increases while on the C atom of the CO<sub>2</sub> molecule decreases (Table S3, ESI<sup>†</sup>). The above two factors collectively point towards the formation of H-bonds between the activated CO<sub>2</sub> and the nearby H<sub>2</sub>O molecules resulting in the enhanced adsorption strength of CO<sub>2</sub> on the catalysts in the presence of water.<sup>75,76</sup>

Our calculations pertaining to CO<sub>2</sub> activation on Ti- and Fe-doped stanene in the presence of two H<sub>2</sub>O molecules simultaneously adsorbed on both sides of the stanene monolayer (Fig. 6) revealed a trend similar to same side co-adsorption of the molecules. For Ti@Sn, the CO<sub>2</sub> activation is well sustained with  $\angle \text{O-C-O}$  129° and C–O bond 1.36 Å, while the same for Fe@Sn are measured as 140° and 1.29 Å, respectively. In this case as well, we observe an increased adsorption strength of CO<sub>2</sub> in the presence of two water molecules compared to dry catalysts:  $E_{\text{ads}}$  is −0.52 eV for Ti@Sn and −0.26 eV for Fe@Sn, similar to co-adsorption of CO<sub>2</sub> and H<sub>2</sub>O on the same side of the catalysts as discussed above.

### 3.4 Charge density difference and Bader charge analysis

**3.4.1 Bare catalysts.** Finally, to understand the observed activity of a few TM SA and the inertness of the remaining TMs, we have performed charge density difference (CDD) calculations and Bader charge analysis<sup>77</sup> for Sc, Ti, and Fe-doped stanene. Fig. 7(a)–(c) depicts the CDD plots for TM-doped stanene without the adsorbed molecules. For Ti and Fe, charge accumulation (yellow region) is clearly visible near the TM and the neighboring Sn atom, which is not present in Sc@Sn. The CDD plots also indicate strong binding of Ti and Fe in the stanene monolayer and hence the stability of the catalysts. The Bader charge calculations revealed that while a charge transfer of 1.30 $e$  occurs from Sc to Sn, the amount of charges transferred between the TM and neighboring Sn atoms are 0.99 $e$  and 0.13 $e$  for Ti and Fe-doped stanene, respectively. The decrease in charge transfer from Sc to Ti and Fe may indicate that Ti and Fe retain excess charge accumulated around them, which can later be transferred to a molecule when adsorbed on the catalyst.

**3.4.2 CO<sub>2</sub> adsorption in the dry phase.** The CDD plots of the complexes with adsorbed CO<sub>2</sub> molecules are shown in Fig. 7(d)–(f). Our Bader charge calculations revealed that there is almost no charge transfer (0.05 $e$ ) from Sc to the CO<sub>2</sub> molecule, also evident from the charge density difference plot

Table 6 TM–C (C of CO<sub>2</sub> molecule) and TM–O (O of H<sub>2</sub>O molecule) distances, C–O–C bond angles, adsorption energies and free energies for CO<sub>2</sub> adsorption in the presence of one water molecule

TM	H <sub>2</sub> O on the opposite side						H <sub>2</sub> O on the same side					
	$d_{\text{TM-C}}$ (Å)	$d_{\text{TM-O}}$ (Å)	$\angle \text{O-C-O}$	C–O (Å)	$E_{\text{ads}}^{\text{CO}_2}$ (eV)	$\Delta G^{\text{CO}_2}$ (eV)	$d_{\text{TM-C}}$ (Å)	$d_{\text{TM-O}}$ (Å)	$\angle \text{O-C-O}$	C–O (Å)	$E_{\text{ads}}^{\text{CO}_2}$ (eV)	$\Delta G^{\text{CO}_2}$ (eV)
Sc	4.82	2.23	180	1.18	−0.15	0.53	4.78	5.64	180	1.18	0.67	1.35
Ti	4.61	2.19	179	1.18	−0.12	0.56	2.04	3.90	127	1.40	−0.39	0.29
Fe	2.06	4.20	149	1.22	0.28	0.96	1.94	3.87	141	1.29	−0.28	0.40

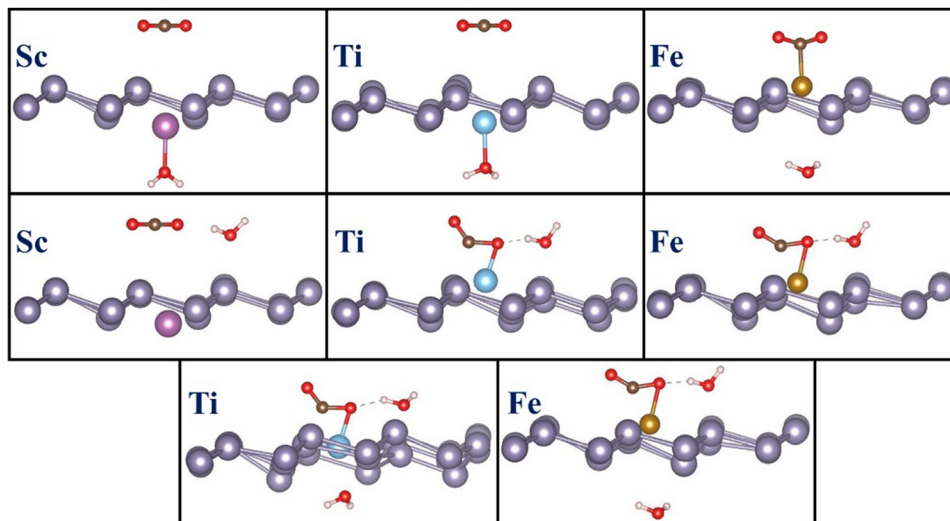


Fig. 6 Co-adsorption of CO<sub>2</sub> and H<sub>2</sub>O on Sc-, Ti- and Fe-doped stanene. CO<sub>2</sub> and one H<sub>2</sub>O on the opposite side (1st panel) and same side (2nd panel) of the catalysts, CO<sub>2</sub> and two H<sub>2</sub>O molecules, on both sides of the catalysts (3rd panel).

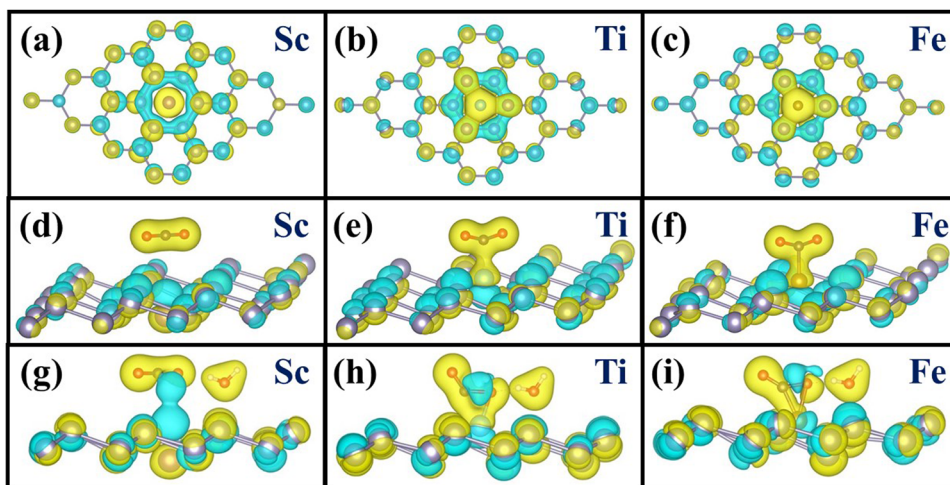


Fig. 7 Charge density difference plots for TM@Sn (1st panel), CO<sub>2</sub> adsorption on TM@Sn (2nd panel) and CO<sub>2</sub> and H<sub>2</sub>O co-adsorption on TM@Sn (3rd panel) with isosurface values 0.005 e Å<sup>-3</sup>, 0.04 e Å<sup>-3</sup> and 0.03 e Å<sup>-3</sup> respectively. Yellow and cyan regions indicate electron accumulation and depletion, respectively.

(Fig. 7d); instead, a charge depletion region is noticed just above the Sc atom. On the other hand, for the Ti doped system, a total of  $0.57e$  has been transferred to CO<sub>2</sub> from the surface, which is further confirmed by the CDD plot in Fig. 7(e). The charge depletion region (in cyan) just beneath the Ti atom further indicates a charge transfer from the Ti atom to a CO<sub>2</sub> molecule. In Fe doped stanene,  $0.46e$  charge has been transferred to CO<sub>2</sub> from the surface. Fig. 7(f) shows that there exists a charge depletion zone below the Fe atom, similar to Ti, indicating that electrons have been transferred from Fe to CO<sub>2</sub> molecules.

**3.4.3 CO<sub>2</sub> adsorption in the presence of water.** Charge density difference and Bader charge calculations have also been carried out for CO<sub>2</sub> adsorption on the catalysts in the presence of H<sub>2</sub>O to investigate if the charge transfers from the

catalyst to CO<sub>2</sub> as observed in the dry phase still persist in the presence of water. Fig. 7(g)–(i) exhibits the CDD plots for CO<sub>2</sub> adsorption in the presence of water on the catalysts. Our calculation revealed that for Sc-doped stanene, there is almost no charge transfer ( $0.04e$ ) to the CO<sub>2</sub> molecule from the catalyst in the presence of water. On the other hand, similar to the dry catalyst, a net charge of  $1.02e$  has been transferred to the CO<sub>2</sub> molecule from Ti, even in the presence of water, as evident from the CDD plot (Fig. 7h). In Fe doped stanene as well, the CO<sub>2</sub> molecule gains  $0.63e$  charge from the surface, clearly revealed from the CDD plot (Fig. 7i). Hence, from the CDD and Bader charge calculations it is apparent that it is the transfer of excess charges from the TM (Ti, Fe) to CO<sub>2</sub> which is responsible for the binding and subsequent activation of the CO<sub>2</sub> molecule, and the observed activity of the catalysts.

## 4 Conclusion

Employing density functional theory, this present work investigates the efficiency of pure and transition metal-doped stanene as catalysts for the CO<sub>2</sub> reduction reaction, investigating the first two electron transfer steps, *i.e.*, reduction of CO<sub>2</sub> to CO. As activation of CO<sub>2</sub> is crucial for the CO<sub>2</sub>RR, we have studied the relative ability of pure and TM-doped stanene to bind and activate CO<sub>2</sub>. Our calculations revealed that only Ti- and Fe-doped stanene bind and activate CO<sub>2</sub> while pristine stanene and the rest of the TM@Sn do not activate the molecule, indicating that activating CO<sub>2</sub> is difficult because of the inert nature of the C=O bond. Our DFT results pertaining to the next hydrogenation steps revealed that the formation of OCHO as a reaction intermediate is preferred over COOH, during the 1st hydrogenation step, leading to HCOOH as the end product for the two-electron-transfer CO<sub>2</sub>RR pathway. This trend is observed in both Ti- and Fe-doped stanene. The selectivity of the catalysts for the CO<sub>2</sub>RR over the competitive HER has also been observed. As the reaction takes place in an aqueous environment, water adsorption on the catalysts and activation of CO<sub>2</sub> in the presence of a water molecule has also been investigated in detail with a particular emphasis on the role of water in simulating CO<sub>2</sub> adsorption on the catalysts. It has been observed that in presence of water, CO<sub>2</sub> adsorption is promoted on the catalyst. The enhanced strength of CO<sub>2</sub> adsorption on the catalysts is attributed to the potential formation of the hydrogen bond between the activated CO<sub>2</sub> and neighboring H<sub>2</sub>O molecule. Finally, to understand the reason behind the activation of CO<sub>2</sub> on Ti- and Fe-doped stanene and the inertness of the rest of the TMs studied, charge density difference and Bader charge analysis have been carried out. While in Ti- and Fe@Sn a substantial charge transfer has been observed from the catalyst to CO<sub>2</sub>, there is almost no charge transfer from the rest of the TM@Sn studied (such as Sc) contributing to their inertness in CO<sub>2</sub> activation. It is evident, hence, from our calculation that the observed activity of a few TMs can be attributed to the charge transfer from the catalyst to the CO<sub>2</sub>. Our results obtained within the DFT framework can be extended to similar materials beyond graphene with improved functionals, for screening efficient 2D catalysts for reduction of CO<sub>2</sub> to CO and beyond.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

SG acknowledges the support from IIITDM Kancheepuram through research assistantship. DM thanks IIITDM Kancheepuram for financial support through institute SEED grant (No: IIITDM/ISG/PHY/7).

## References

- 1 N.-N. Vu, S. Kaliaguine and T.-O. Do, Critical Aspects and Recent Advances in Structural Engineering of Photocatalysts

- for Sunlight-Driven Photocatalytic Reduction of CO<sub>2</sub> into Fuels, *Adv. Funct. Mater.*, 2019, **29**, 1901825.
- 2 S. K. Kuk, R. K. Singh, D. H. Nam, R. Singh, J.-K. Lee and C. B. Park, Photoelectrochemical Reduction of Carbon Dioxide to Methanol through a Highly Efficient Enzyme Cascade, *Angew. Chem., Int. Ed.*, 2017, **56**, 3827–3832.
- 3 Z. Zhang, S.-Y. Pan, H. Li, J. Cai, A. G. Olabi, E. J. Anthony and V. Manovic, Recent advances in carbon dioxide utilization, *Renewable Sustainable Energy Rev.*, 2020, **125**, 109799.
- 4 S. C. Peter, Reduction of CO<sub>2</sub> to Chemicals and Fuels: A Solution to Global Warming and Energy Crisis, *ACS Energy Lett.*, 2018, **3**, 1557–1561.
- 5 A. Saravanan, P. Senthil kumar, D.-V. N. Vo, S. Jeevanantham, V. Bhuvaneshwari, V. Anantha Narayanan, P. R. Yaashikaa, S. Swetha and B. Reshma, A comprehensive review on different approaches for CO<sub>2</sub> utilization and conversion pathways, *Chem. Eng. Sci.*, 2021, **236**, 116515.
- 6 A. Mustafa, B. G. Lougou, Y. Shuai, Z. Wang and H. Tan, Current technology development for CO<sub>2</sub> utilization into solar fuels and chemicals: a review, *J. Energy Chem.*, 2020, **49**, 96–123.
- 7 S. Samanta and R. Srivastava, Catalytic conversion of CO<sub>2</sub> to chemicals and fuels: the collective thermocatalytic/photocatalytic/electrocatalytic approach with graphitic carbon nitride, *Mater. Adv.*, 2020, **1**, 1506–1545.
- 8 R. Daiyan, W. H. Saputera, H. Masood, J. Leverett, X. Lu and R. Amal, A Disquisition on the Active Sites of Heterogeneous Catalysts for Electrochemical Reduction of CO<sub>2</sub> to Value-Added Chemicals and Fuel, *Adv. Energy Mater.*, 2020, **10**, 1902106.
- 9 D. Sharma, R. Sharma, D. Chand and A. Chaudhary, Nanocatalysts as potential candidates in transforming CO<sub>2</sub> into valuable fuels and chemicals: a review, *Environ. Nanotechnol. Monit. Manage.*, 2022, **18**, 100671.
- 10 H. S. Whang, J. Lim, M. S. Choi, J. Lee and H. Lee, Heterogeneous catalysts for catalytic CO<sub>2</sub> conversion into value-added chemicals, *BMC Chem. Eng.*, 2019, **1**, 9.
- 11 S. A. Mazari, N. Hossain, W. J. Basirun, N. M. Mubarak, R. Abro, N. Sabzoi and A. Shah, An overview of catalytic conversion of CO<sub>2</sub> into fuels and chemicals using metal organic frameworks, *Process Saf. Environ. Prot.*, 2021, **149**, 67–92.
- 12 D. Gao, W. Li, H. Wang, G. Wang and R. Cai, Heterogeneous Catalysis for CO<sub>2</sub> Conversion into Chemicals and Fuels, *Trans. Tianjin Univ.*, 2022, **28**, 245–264.
- 13 Y. Ling, Q. Ma, Y. Yu and B. Zhang, Optimization Strategies for Selective CO<sub>2</sub> Electroreduction to Fuels, *Trans. Tianjin Univ.*, 2021, **27**, 180–200.
- 14 Q. Cui, G. Qin, W. Wang, K. R. Geethalakshmi, A. Du and Q. Sun, Novel two-dimensional MOF as a promising single-atom electrocatalyst for CO<sub>2</sub> reduction: a theoretical study, *Appl. Surf. Sci.*, 2020, **500**, 143993.
- 15 C. Yang, S. Li, Z. Zhang, H. Wang, H. Liu, F. Jiao, Z. Guo, X. Zhang and W. Hu, Organic-Inorganic Hybrid Nanomaterials for Electrocatalytic CO<sub>2</sub> Reduction, *Small*, 2020, **16**, 2001847.
- 16 W. da Silva Freitas, A. D'Epifanio and B. Mecheri, Electrocatalytic CO<sub>2</sub> reduction on nanostructured metal-based

- materials: challenges and constraints for a sustainable pathway to decarbonization, *J. CO<sub>2</sub> Util.*, 2021, **50**, 101579.
- 17 M. N. Hossain, J. Wen and A. Chen, Unique copper and reduced graphene oxide nanocomposite toward the efficient electrochemical reduction of carbon dioxide, *Sci. Rep.*, 2017, **7**, 3184.
  - 18 S. Lu, F. Lou and Z. Yu, Recent Progress in Two-Dimensional Materials for Electrocatalytic CO<sub>2</sub> Reduction, *Catalysts*, 2022, **12**, 228.
  - 19 Y. Wang, Y. Li, J. Liu, C. Dong, C. Xiao, L. Cheng, H. Jiang, H. Jiang and C. Li, BiPO<sub>4</sub>-Derived 2D Nanosheets for Efficient Electrocatalytic Reduction of CO<sub>2</sub> to Liquid Fuel, *Angew. Chem., Int. Ed.*, 2021, **60**, 7681–7685.
  - 20 S. Payra, S. Shenoy, C. Chakraborty, K. Tarafder and S. Roy, Structure-Sensitive Electrocatalytic Reduction of CO<sub>2</sub> to Methanol over Carbon-Supported Intermetallic PtZn Nano-Alloys, *ACS Appl. Mater. Interfaces*, 2020, **12**, 19402–19414.
  - 21 X. Duan, J. Xu, Z. Wei, J. Ma, S. Guo, S. Wang, H. Liu and S. Dou, Metal-Free Carbon Materials for CO<sub>2</sub> Electrochemical Reduction, *Adv. Mater.*, 2017, **29**, 1701784.
  - 22 H. A. Hansen, J. B. Varley, A. A. Peterson and J. K. Nørskov, Understanding Trends in the Electrocatalytic Activity of Metals and Enzymes for CO<sub>2</sub> Reduction to CO, *J. Phys. Chem. Lett.*, 2013, **4**, 388–392.
  - 23 R. Küngas, Review—Electrochemical CO<sub>2</sub> Reduction for CO Production: Comparison of Low- and High-Temperature Electrolysis Technologies, *J. Electrochem. Soc.*, 2020, **167**, 044508.
  - 24 X. Liu and L. Dai, Carbon-based metal-free catalysts, *Nat. Rev. Mater.*, 2016, **1**, 1–12.
  - 25 F. Li, L. Chen, G. P. Knowles, D. R. MacFarlane and J. Zhang, Hierarchical Mesoporous SnO<sub>2</sub> Nanosheets on Carbon Cloth: A Robust and Flexible Electrocatalyst for CO<sub>2</sub> Reduction with High Efficiency and Selectivity, *Angew. Chem., Int. Ed.*, 2017, **56**, 505–509.
  - 26 R. Paul, L. Zhu, H. Chen, J. Qu and L. Dai, Recent Advances in Carbon-Based Metal-Free Electrocatalysts, *Adv. Mater.*, 2019, **31**, 1806403.
  - 27 D. Misra and S. K. Yadav, Nb-Implanted BaO as a Support for Gold Single Atoms, *J. Phys. Chem. C*, 2021, **125**, 28059–28066.
  - 28 W. Kong, J. Deng and L. Li, Recent advances in noble metal MXene-based catalysts for electrocatalysis, *J. Mater. Chem. A*, 2022, **10**, 14674–14691.
  - 29 C. Anichini, W. Czepa, D. Pakulski, A. Aliprandi, A. Ciesielski and P. Samorì, Chemical sensing with 2D materials, *Chem. Soc. Rev.*, 2018, **47**, 4860–4908.
  - 30 D. Akinwande, C. J. Brennan, J. S. Bunch, P. Egberts, J. R. Felts, H. Gao, R. Huang, J.-S. Kim, T. Li, Y. Li, K. M. Liechti, N. Lu, H. S. Park, E. J. Reed, P. Wang, B. I. Yakobson, T. Zhang, Y.-W. Zhang, Y. Zhou and Y. Zhu, A review on mechanics and mechanical properties of 2D materials—Graphene and beyond, *Extreme Mech. Lett.*, 2017, **13**, 42–77.
  - 31 R. Hu, G. Liao, Z. Huang, H. Qiao, H. Liu, Y. Shu, B. Wang and X. Qi, Recent advances of monoelemental 2D materials for photocatalytic applications, *J. Hazard. Mater.*, 2021, **405**, 124179.
  - 32 T. Wang, H. Wang, Z. Kou, W. Liang, X. Luo, F. Verpoort, Y.-J. Zeng and H. Zhang, Xenos as an Emerging 2D Monoelemental Family: Fundamental Electrochemistry and Energy Applications, *Adv. Funct. Mater.*, 2020, **30**, 2002885.
  - 33 H. Qiao, H. Liu, Z. Huang, R. Hu, Q. Ma, J. Zhong and X. Qi, Tunable Electronic and Optical Properties of 2D Monoelemental Materials Beyond Graphene for Promising Applications, *Energy Environ. Mater.*, 2021, **4**, 522–543.
  - 34 X. Chen, C. Tan, Q. Yang, R. Meng, Q. Liang, M. Cai, S. Zhang and J. Jiang, Ab Initio Study of the Adsorption of Small Molecules on Stanene, *J. Phys. Chem. C*, 2016, **120**, 13987–13994.
  - 35 K. Ma, J. Chen, X. Dai, J. Xiao, L. Wang, L. Xu and Z. Wang, The potential of stanene with transition metal adsorbed as a promising gas sensor: a first-principles study, *Results Phys.*, 2021, **28**, 104617.
  - 36 A. Zhang, H. Yang, Q. Liu, W. Li and Y. Wang, DFT insights into the adsorption properties of toxic gas molecules on pure and transition metal embedded stanene monolayers: towards gas sensor devices, *Synth. Met.*, 2020, **266**, 116441.
  - 37 J. Zhou, D. Liu, F. Wu, L. Yang, Y. Xiong and A. Abbasi, A DFT study on the possibility of embedding a single Ti atom into the perfect stanene monolayer as a highly efficient gas sensor, *Theor. Chem. Acc.*, 2020, **139**, 46.
  - 38 Y.-Z. Chang, J.-N. Lin, S.-D. Li and H. Liu, Adsorption of greenhouse gases (methane and carbon dioxide) on the pure and Pd-adsorbed stanene nanosheets: a theoretical study, *Surf. Interfaces*, 2021, **22**, 100878.
  - 39 A. Abbasi and J. J. Sardroodi, Density functional theory investigation of the interactions between the buckled stanene nanosheet and XO<sub>2</sub> gases (X = N, S, C), *Comput. Theor. Chem.*, 2018, **1125**, 15–28.
  - 40 H. Vovusha, T. Hussain, M. Sajjad, H. Lee, A. Karton, R. Ahuja and U. Schwingenschlögl, Sensitivity enhancement of stanene towards toxic SO<sub>2</sub> and H<sub>2</sub>S, *Appl. Surf. Sci.*, 2019, **495**, 143622.
  - 41 G. Kresse and J. Hafner, Ab initio molecular dynamics for liquid metals, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **47**, 558–561.
  - 42 P. E. Blöchl, Projector augmented-wave method, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953–17979.
  - 43 G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11186.
  - 44 J. P. Perdew, K. Burke and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
  - 45 S. Grimme, J. Antony, S. Ehrlich and H. Krieg, A consistent and accurate ab initio parametrization of density functional dispersion correction (DFT-D) for the 94 elements H-Pu, *J. Chem. Phys.*, 2010, **132**, 154104.
  - 46 X. Li, H. Li, X. Zuo, L. Kang, D. Li, B. Cui and D. Liu, Chemically Functionalized Penta-stanene Monolayers for Light Harvesting with High Carrier Mobility, *J. Phys. Chem. C*, 2018, **122**, 21763–21769.
  - 47 A. Abbasi and J. J. Sardroodi, Electronic structure tuning of stanene monolayers from DFT calculations: effects of substitutional elemental doping, *Appl. Surf. Sci.*, 2018, **456**, 290–301.

- 48 S. R. Naqvi, T. Hussain, W. Luo and R. Ahuja, Exploring Doping Characteristics of Various Adatoms on Single-Layer Stanene, *J. Phys. Chem. C*, 2017, **121**, 7667–7676.
- 49 J. Chen, Z. Wang, X. Dai, J. Xiao, M. Long and T. Chen, The effects of transition metal adatoms on the electronic properties of stanene, *Phys. E*, 2020, **124**, 114365.
- 50 A. Abbasi, Theoretical Investigation of The interaction Between Noble Metals (Ag, Au, Pd, Pt) and Stanene Nanosheets: A DFT Study, *J. Inorg. Organomet. Polym. Mater.*, 2019, **29**, 1895–1915.
- 51 H. J. Monkhorst and J. D. Pack, Special points for Brillouin-zone integrations, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1976, **13**, 5188–5192.
- 52 D. Misra, G. Di Liberto and G. Pacchioni, CO<sub>2</sub> electroreduction on single atom catalysts: is water just a solvent?, *J. Catal.*, 2023, **422**, 1–11.
- 53 S. Wang, L. Li, J. Li, C. Yuan, Y. Kang, K. S. Hui, J. Zhang, F. Bin, X. Fan, F. Chen and K. N. Hui, High-Throughput Screening of Nitrogen-Coordinated Bimetal Catalysts for Multi-electron Reduction of CO<sub>2</sub> to CH<sub>4</sub> with High Selectivity and Low Limiting Potential, *J. Phys. Chem. C*, 2021, **125**, 7155–7165.
- 54 A. A. Peterson, F. Abild-Pedersen, F. Studt, J. Rossmeisl and J. K. Nørskov, How copper catalyzes the electroreduction of carbon dioxide into hydrocarbon fuels, *Energy Environ. Sci.*, 2010, **3**, 1311–1315.
- 55 S. Zhou, W. Pei, J. Zhao and A. Du, Silicene catalysts for CO<sub>2</sub> hydrogenation: the number of layers controls selectivity, *Nanoscale*, 2019, **11**, 7734–7743.
- 56 M. Wang, L. Kong, X. Lu and C.-M. L. Wu, First-row transition metal embedded pyrazine-based graphynes as high-performance single atom catalysts for the CO<sub>2</sub> reduction reaction, *J. Mater. Chem. A*, 2022, **10**, 9048–9058.
- 57 H. Li, D. Wu, J. Wu, Y. Song, W. Lv, Z. Duan and D. Ma, Mechanistic understanding of the electrocatalytic conversion of CO into C<sup>2+</sup> products by double-atom catalysts, *Mater. Today Phys.*, 2023, **37**, 101203.
- 58 D. Wu, P. Lv, J. Wu, B. He, X. Li, K. Chu, Y. Jia and D. Ma, Catalytic active centers beyond transition metals: atomically dispersed alkaline-earth metals for the electroreduction of nitrate to ammonia, *J. Mater. Chem. A*, 2023, **11**, 1817–1828.
- 59 J. Lin, Z. Pan and X. Wang, Photochemical Reduction of CO<sub>2</sub> by Graphitic Carbon Nitride Polymers, *ACS Sustainable Chem. Eng.*, 2014, **2**, 353–358.
- 60 X. Su, X.-F. Yang, Y. Huang, B. Liu and T. Zhang, Single-Atom Catalysis toward Efficient CO<sub>2</sub> Conversion to CO and Formate Products, *Acc. Chem. Res.*, 2019, **52**, 656–664.
- 61 U. J. Etim, C. Zhang and Z. Zhong, Impacts of the Catalyst Structures on CO<sub>2</sub> Activation on Catalyst Surfaces, *Nanomaterials*, 2021, **11**, 3265.
- 62 Y. Wang, D. He, H. Chen and D. Wang, Catalysts in electro-, photo- and photoelectrocatalytic CO<sub>2</sub> reduction reactions, *J. Photochem. Photobiol., C*, 2019, **40**, 117–149.
- 63 Y. Quan, J. Zhu and G. Zheng, Electrocatalytic Reactions for Converting CO<sub>2</sub> to Value-Added Products, *Small Sci.*, 2021, **1**, 2100043.
- 64 M. Ma, F. Li and Q. Tang, Coordination environment engineering on nickel single-atom catalysts for CO<sub>2</sub> electroreduction, *Nanoscale*, 2021, **13**, 19133–19143.
- 65 L. Gong, X. Wang, T. Zheng, J. Liu, J. Wang, Y.-C. Yang, J. Zhang, X. Han, L. Zhang and Z. Xia, Catalytic mechanism and design principle of coordinately unsaturated single metal atom-doped covalent triazine frameworks with high activity and selectivity for CO<sub>2</sub> electroreduction, *J. Mater. Chem. A*, 2021, **9**, 3555–3566.
- 66 T. Liu, G. Wang and X. Bao, Electrochemical CO<sub>2</sub> Reduction Reaction on 3d Transition Metal Single-Atom Catalysts Supported on Graphdiyne: A DFT Study, *J. Phys. Chem. C*, 2021, **125**, 26013–26020.
- 67 D. Bohra, I. Ledezma-Yanez, G. Li, W. de Jong, E. A. Pidko and W. A. Smith, Lateral Adsorbate Interactions Inhibit HCOO<sup>-</sup> while Promoting CO Selectivity for CO<sub>2</sub> Electrocatalysis on Silver, *Angew. Chem.*, 2019, **131**, 1359–1363.
- 68 S. Back, J. Lim, N.-Y. Kim, Y.-H. Kim and Y. Jung, Single-atom catalysts for CO<sub>2</sub> electroreduction with significant activity and selectivity improvements, *Chem. Sci.*, 2017, **8**, 1090–1096.
- 69 C. Ling, Q. Li, A. Du and J. Wang, Computation-Aided Design of Single-Atom Catalysts for One-Pot CO<sub>2</sub> Capture, Activation, and Conversion, *ACS Appl. Mater. Interfaces*, 2018, **10**, 36866–36872.
- 70 S. Vijay, W. Ju, S. Brückner, S.-C. Tsang, P. Strasser and K. Chan, Unified mechanistic understanding of CO<sub>2</sub> reduction to CO on transition metal and single atom catalysts, *Nat. Catal.*, 2021, **4**, 1024–1031.
- 71 C. Zhao, X. Su, S. Wang, Y. Tian, L. Yan and Z. Su, Single-atom catalysts on supported silicomolybdic acid for CO<sub>2</sub> electroreduction: a DFT prediction, *J. Mater. Chem. A*, 2022, **10**, 6178–6186.
- 72 X. Wan, Z. Zhang, H. Niu, Y. Yin, C. Kuai, J. Wang, C. Shao and Y. Guo, Machine-Learning-Accelerated Catalytic Activity Predictions of Transition Metal Phthalocyanine Dual-Metal-Site Catalysts for CO<sub>2</sub> Reduction, *J. Phys. Chem. Lett.*, 2021, **12**, 6111–6118.
- 73 A. K. Srivastava and N. Misra, Calculating interaction energies of hydrogen bonded dimers and complexes of HF, H<sub>2</sub>O and NH<sub>3</sub>: Super-molecular *versus* AIM Approach, *J. Comput. Methods Mol. Des.*, 2014, **4**, 19–23.
- 74 L. Bondesson, K. V. Mikkelsen, Y. Luo, P. Garberg and H. Ågren, Hydrogen bonding effects on infrared and Raman spectra of drug molecules, *Spectrochim. Acta, Part A*, 2007, **66**, 213–224.
- 75 D. Zhao and X. Liu, Density Functional Calculation of H<sub>2</sub>O/CO<sub>2</sub>/CH<sub>4</sub> for Oxygen-Containing Functional Groups in Coal Molecules, *ACS Omega*, 2022, **7**, 17330–17338.
- 76 Biochem 104b Lecture Notes, [https://www.bio.brandeis.edu/classes/biochem104/lecture\\_notes.html](https://www.bio.brandeis.edu/classes/biochem104/lecture_notes.html), (accessed November 28, 2023).
- 77 G. Henkelman, A. Arnaldsson and H. Jónsson, A fast and robust algorithm for Bader decomposition of charge density, *Comput. Mater. Sci.*, 2006, **36**, 354–360.