





## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Catal. Sci. Technol.*, 2024,  
14, 4948Structural dynamics of PtSn/SiO<sub>2</sub> for propane  
dehydrogenation†Kewei Yu, <sup>ab</sup> Matthew Scarpelli,<sup>a</sup> Sagar Sourav,<sup>ab</sup> Alfred Worrad,<sup>ab</sup>  
J. Anibal Boscoboinik, <sup>c</sup> Lu Ma,<sup>d</sup> Steven N. Ehrlich,<sup>d</sup> Nebojsa Marinkovic,<sup>d</sup>  
Weiqing Zheng <sup>\*ab</sup> and Dionisios G. Vlachos <sup>\*ab</sup>

PtSn bimetallic catalysts are among the best-performing propane dehydrogenation (PDH) catalysts. However, understanding these catalysts remains limited due to the intricate nature of bimetallic systems and their dynamic structural evolution under reaction conditions. To address this challenge, we employ various *in situ/operando* techniques, including UV-vis, CO diffuse reflective infrared Fourier transform spectroscopy (CO-DRIFTS), near ambient pressure X-ray photoelectron spectroscopy (NAP-XPS), and *operando* X-ray absorption spectroscopy (XAS), to elucidate the structural dynamics of PtSn/SiO<sub>2</sub> catalysts under reduction and working conditions. Our investigation reveals that the interactions between Pt, Sn, and SiO<sub>2</sub> support are strongly influenced by the synthesis procedures and the initial catalyst structure. Exposure to H<sub>2</sub> causes a reversible Sn–OH formation observed by modulation excitation spectroscopy (MES). A sequentially impregnated catalyst with a nominal Pt:Sn ratio of 1:3 and a co-impregnated catalyst with a ratio of 1:2 exhibit optimal performance for PDH. Despite distinct synthesis procedures and bulk structures, these two catalysts exhibit comparable surface properties and PDH performance, attributed to the dynamic migration of Sn species and formation of a Pt-rich metal surface under reductive atmospheres.

Received 7th June 2024,  
Accepted 24th July 2024

DOI: 10.1039/d4cy00725e

[rsc.li/catalysis](https://rsc.li/catalysis)

## 1 Introduction

Propylene is a crucial petrochemical product with high demand globally.<sup>1–4</sup> Propane dehydrogenation (PDH) has become economically viable with the shale gas revolution. Considerable research efforts have been devoted to developing and enhancing PDH catalysts.<sup>1,3,5</sup> Among these, Pt-based catalysts are top-performing despite their relatively high cost.<sup>6</sup> PtSn-based catalysts, in particular, have been commercialized due to their remarkable activity and selectivity.<sup>1,7,8</sup> The synergistic effect between Pt and Sn, attributed to geometric and electronic factors, is pivotal to their superior performance.<sup>1,9</sup> Specifically, Sn atoms break large Pt ensembles, suppressing structure-sensitive side reactions like coke formation. Additionally, they facilitate

electron transfer to the Pt 5d band, weakening the adsorption of coke precursors, such as ethylene, leading to more facile olefin desorption.<sup>1</sup> However, the exact mechanisms behind Sn's promotional effects and the most active phase remain unclear due to the structural complexity of supported bimetallics.

According to the Pt–Sn phase diagram, five Pt–Sn intermetallic phases exist alongside individual Pt and Sn species.<sup>10–12</sup> Realistic catalysts usually comprise a mixture of these species with different sizes, depending on the synthesis, manifesting the system complexity. Numerous catalyst structures have been proposed. For example, Liu *et al.* suggested partially reduced Sn species interacting with Pt clusters at the metal/support interface on MFI zeolite,<sup>13</sup> and found that smaller PtSn clusters perform better than nanoparticles.<sup>14</sup> Ye *et al.* suggested that Sn–Pt sequential impregnation leads to Pt nanoparticles with a hexagonal Pt<sub>1</sub>–Sn<sub>1</sub> intermetallic shell,<sup>12</sup> whereas Deng *et al.* found that Pt–Sn sequential impregnation renders a Pt–Sn alloy core and Sn-rich surface coexisting with SnO<sub>2</sub> species.<sup>15</sup> Xu *et al.*, on the other hand, demonstrated that the supported PtSn nanoparticles possess a significant compositional variation.<sup>16</sup> All these structural variances give rise to distinct catalytic properties of these catalysts. Further adding to the complexity is that the distribution of Pt and Sn, and consequently the

<sup>a</sup> Department of Chemical and Biomolecular Engineering, University of Delaware, 150 Academy St., Newark, DE, USA. E-mail: [weiqing@udel.edu](mailto:weiqing@udel.edu), [vlachos@udel.edu](mailto:vlachos@udel.edu)<sup>b</sup> Delaware Energy Institute, University of Delaware, 221 Academy St., Newark, DE, USA<sup>c</sup> Center for Functional Nanomaterials, Brookhaven National Laboratory, Upton, NY 11973, USA<sup>d</sup> National Synchrotron Light Source, Brookhaven National Laboratory, Upton, NY 11973, USA† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4cy00725e>

prevalence of these species, can change dynamically with the reaction conditions. For example, Wang *et al.* used an acid to etch away the surface Sn species, revealing that the nanoparticle surface can self-adjust to a  $\text{Pt}_3\text{Sn}_1$  configuration regardless of the bulk nanoparticle composition after reduction.<sup>17</sup> Xing *et al.* found a  $\text{Sn}_1\text{Pt}$  single-atom alloy phase forming after reduction, which evolves into a  $\text{Pt}_3\text{Sn}_1$  phase during PDH.<sup>18</sup> This dynamic behavior renders traditional *ex situ* characterizations inadequate for building structure–performance relations. Therefore, it is crucial to monitor the catalyst structure *in situ/operando* to capture the catalyst structure dynamics, and to identify the true active phase.

Recently, Motagamwala *et al.* reported a highly stable and selective  $\text{PtSn/SiO}_2$  PDH catalyst capable of operating at the thermodynamic limit with minimal deactivation.<sup>19</sup> The superior performance was attributed to the weak interaction of  $\text{PtSn}$  nanoparticles with  $\text{SiO}_2$ . Our study aims to delve into this catalyst and understand the  $\text{Pt-Sn-SiO}_2$  interactions by comparing catalysts synthesized with different methods and  $\text{Pt:Sn}$  ratios using *in situ/operando* techniques. We monitor the structure dynamics of the catalysts *via* techniques including UV-vis, CO diffuse reflective infrared Fourier transform spectroscopy (CO-DRIFTS), near ambient pressure X-ray photoelectron spectroscopy (NAP-XPS), and *operando* X-ray absorption spectroscopy (XAS). Alloyed  $\text{PtSn}$  is observed in the co-impregnated catalyst, while separated phases dominate the sequentially impregnated ones. Sn dynamics is revealed during the reduction process, engaging in stronger interactions with  $\text{SiO}_2$ , elucidating key factors underlying the catalyst's superior performance and the optimal surface compositional range.

## 2 Materials and methods

### 2.1 Catalyst synthesis

$\text{PtSn/SiO}_2$  with various Pt and Sn ratios were synthesized through incipient wetness impregnation (IWI).  $\text{SiO}_2$  (Fuji Silysia G6) was calcined at 700 °C for 1 h prior to impregnation. For sequentially impregnated samples,  $\text{SnCl}_2$  aqueous solution with a  $\text{SnCl}_2:\text{HCl}$  molar ratio of 1:3 (made with concentrated HCl,  $\text{SnCl}_2\cdot 2\text{H}_2\text{O}$ , and DI water) was first impregnated into 1 g of  $\text{SiO}_2$ . The resulting powder was subsequently dried under atmospheric conditions for 24 h before further drying at 120 °C in an air oven for 4 h and calcination at 500 °C for 3 h using a muffle furnace. The resulting powder is denoted as  $\text{Sn/SiO}_2$ . Pt was introduced by impregnating an  $\text{H}_2\text{PtCl}_6$  aqueous solution on  $\text{Sn/SiO}_2$  with the same subsequent drying process described above. The dried catalyst was directly reduced at 600 °C in 10%  $\text{H}_2$  for 2 h to obtain the final catalyst  $\text{PtSn/SiO}_2\text{-seq.}$  For co-impregnated samples, the  $\text{SnCl}_2$  and  $\text{H}_2\text{PtCl}_6$  aqueous solutions were premixed and then impregnated into 1 g of  $\text{SiO}_2$ . The resulting powder was subsequently dried under atmospheric conditions for 24 h before further drying at 120 °C in an air oven for 4 h. The dried powder was directly reduced in 10%  $\text{H}_2/\text{He}$  atmosphere at 600 °C for 2 h to obtain

the final catalyst  $\text{PtSn/SiO}_2\text{-co.}$  The nominal loading of Pt in all catalysts was 2 wt%. Nominal Sn loadings were varied with the atomic ratio of Pt and Sn indicated as  $x\text{Pt}_y\text{Sn}$ . Some catalysts were also calcined at 500 °C and then reduced in 10%  $\text{H}_2$  at 600 °C for comparison.

### 2.2 Characterizations

**2.2.1 X-Ray characterization.** X-ray diffraction (XRD) was performed on an X-ray powder diffractometer (Bruker D8) equipped with a monochromatic  $\text{Cu-K}\alpha$  source, over a  $2\theta$  range of 10–80° with a step size of 0.05° and 1 s per step.

X-ray photoelectron spectroscopy (XPS) data was obtained using a Thermo Fisher K-Alpha+ XPS system equipped with an  $\text{Al-K}\alpha$  X-ray monochromatic source and a hemispherical analyzer. Near ambient pressure (NAP) XPS was measured in a lab-based XPS system from Specs, capable of measuring at gas pressures up to ~2 mbar and sample temperatures from –180 °C to 1000 °C, equipped with monochromated Al (1486.6 eV) X-ray source.

X-ray absorption spectroscopy (XAS) was performed at NSLS-II 7-BM QAS at Brookhaven National Laboratory. Samples were pelletized into discs of 11 mm diameter and heated in a Linkam HFS600E-PB4 stage (–195–600 °C). A portable gas handling system was used to supply certain gases to sample reactors. Data was collected in fluorescence mode.

**2.2.2 Spectroscopies.** *In situ* pyridine Fourier-transform infrared spectroscopy (FTIR) was conducted in a custom-made transmission glass cell of a Nicolet iS50 FTIR spectrometer (Thermo Fisher Scientific). The catalyst was first pressed into a thin pellet and degassed in the IR cell in vacuum at 300 °C for 1 h. After degassing, the cell was ramped down to 150 °C. Samples were first saturated with pyridine and then evacuated to leave behind chemisorbed species and spectra acquisition. The sample was reduced in a furnace and immediately transferred to the cell to minimize oxidation.

*In situ* CO DRIFTS was conducted in a Praying Mantis high-temperature reaction chamber and measured *in situ* with a Nicolet iS50 FTIR spectrometer. The samples were loaded in the cell and reduced in 10%  $\text{H}_2$  at 600 °C for 30 min and ramped to 400 °C. The gas was then switched to 10%  $\text{H}_2$ , 1% CO balanced by Ar. Spectra were measured during ramp down every 50 °C.

Diffuse-reflectance UV-visible (DR UV-vis) spectra were recorded with an AVANTES AvaSpec-ULS2048CLEVO-RS spectrometer equipped with an AvaLight-XE light source.

Modulation excitation spectroscopy (MES) was conducted in a custom-made low-dead volume spectroscopic cell.<sup>20</sup> The gas flow was regulated using 8 thermal mass flow controllers (Brooks Instrument). Gas switching was realized by two 4-port/2-position switching valves (VICI Valco). Time-series data, including UV-vis and DRIFTS spectra, were Fourier-transformed, and only the fundamental frequency was chosen to obtain the phase domain spectra after the inverse-Fourier transform. The gases are switched between 10%  $\text{H}_2$  in Ar or 10%  $\text{O}_2$  in Ar, 50 sccm total, with a switching period



of 120 s (60 s per switch). Typically, an integration time of 100 ms and an averaging number of 10 are used for UV-vis measurement. An integration time of  $\sim 9$  ms is used for DRIFTS measurement. The MES spectroscopic data were analyzed with software developed by our group, available on GitHub at <https://github.com/worradal/wavey>.

**2.2.3 Electron microscopy.** High-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) was conducted on a JEOL NEOARM electron microscope equipped with a spherical aberration corrector and two Energy-Dispersive X-Ray Spectroscopy (EDS) detectors operating at 200 kV.

Bright-field high-resolution transmission electron microscopy (BF-HRTEM) was conducted on a JEOL 2010F transmission electron microscope with a field emission gun emitter at 200 kV. Samples were diluted in acetone and deposited on a lacey carbon film on copper grids provided by the Electron Microscopy Sciences. *In situ* heating experiments were conducted with a vacuum heating holder (Protochips) with a thermal E-chip (Protochips, Fusion) in JEOL 2010F.

### 2.3 Catalytic performance evaluation

Non-oxidative PDH reactions were conducted in an atmospheric pressure continuous flow tubular quartz reactor of 7 mm inner diameter. Typically, 50 mg pelletized catalyst (40–60 mesh) were mixed with quartz pellets to form a catalyst bed 15 mm in length. The bed was fixed by quartz wool and quartz pellets above and below it. The  $C_3H_8$ , He, and  $H_2$  flows were regulated by calibrated thermal mass flow controllers from MKS Instruments. Typical flow was 5 sccm  $C_3H_8$  balanced by He, totaling 54.2 sccm.

Conversion and selectivity were calculated based on the differences in inlet and outlet gas compositions. As shown in eqn (1) and (2),  $[C_3H_8]_0$  represents the inlet propane concentration; terms without the subscript represent outlet concentrations. The change in volumetric flow rate is neglected due to the high dilution. The carbon balance was  $100 \pm 5\%$  in all cases.

$$X_{C_3H_8} (\%) = \frac{[C_3H_8]_0 - [C_3H_8]}{[C_3H_8]_0} \times 100\% \quad (1)$$

$$S_{C_3H_6} (\%) = \frac{3 \times [C_3H_6]_0}{3 \times [C_3H_6] + 2 \times [C_2H_6] + 2 \times [C_2H_4] + [CH_4]} \times 100\% \quad (2)$$

## 3 Results and discussion

### 3.1 Sn–SiO<sub>2</sub> interactions in Sn/SiO<sub>2</sub> and 1Pt3Sn/SiO<sub>2</sub>-seq


It has been hypothesized that the weak interaction between Pt, Sn, and the support is essential for the stability of Pt–Sn bimetallic catalysts.<sup>19,21–23</sup> To vary the Pt–Sn interactions, we synthesize PtSn/SiO<sub>2</sub> catalysts with different Pt:Sn ratios by co-impregnation and sequential impregnation as described in section 2.1.

Structural characterizations of Sn/SiO<sub>2</sub> were conducted to elucidate the nature of Sn species on the SiO<sub>2</sub> support and

their interactions. Sn/SiO<sub>2</sub> has been extensively investigated for various acid-catalyzed reactions, typically containing Sn<sup>4+</sup> species as the Lewis acid site.<sup>24–28</sup> The sample underwent calcination in air at 500 °C (denoted as Sn/SiO<sub>2</sub>-500C) and then was impregnated with Pt precursor when the sequentially impregnated PtSn/SiO<sub>2</sub> catalyst was made. In Fig. 1a, the XRD data of fresh Sn/SiO<sub>2</sub> post-calcination exhibits a pattern like that of the bare SiO<sub>2</sub> support, indicating the highly dispersed Sn species, most likely in the form of Sn<sup>4+</sup>, or small clusters below 3 nm. Minor diffraction patterns corresponding to tetragonal rutile SnO<sub>2</sub> exist (black triangles), suggesting the presence of small-sized crystalline SnO<sub>2</sub> clusters. EDS mapping analysis of Sn/SiO<sub>2</sub> in Fig. S2† shows the uniform dispersion of Sn over the support, while the HRTEM images confirm the existence of SnO<sub>2</sub> clusters (Fig. S1a†).

However, after the reduction of Sn/SiO<sub>2</sub> at 600 °C in 10% H<sub>2</sub> (denoted as Sn/SiO<sub>2</sub>-500C-600R), the SnO<sub>2</sub> clusters vanish in XRD (Fig. 1a) and TEM (Fig. S1b†). Due to the facile reduction of SnO<sub>2</sub>,<sup>29,30</sup> it is likely that SnO<sub>2</sub> clusters got reduced to SnO and subsequently diffused into the porous SiO<sub>2</sub> support.<sup>31</sup> *In situ* reduction of Sn/SiO<sub>2</sub> was conducted with a TEM holder capable of heating in vacuum, using the electron beam as the reducing agent.<sup>32</sup> As shown in Fig. S3,† at 600 °C, the SnO<sub>2</sub> clusters undergo gradual reduction and disappear after 40 min of heating. Sn species may be prone to evaporation in vacuum under electron beam irradiation, affirming the high mobility of reduced Sn species at high temperatures.

Pyridine FTIR shed light on the surface chemical properties of Sn/SiO<sub>2</sub>. In Fig. 1b, adsorbed pyridine exhibits

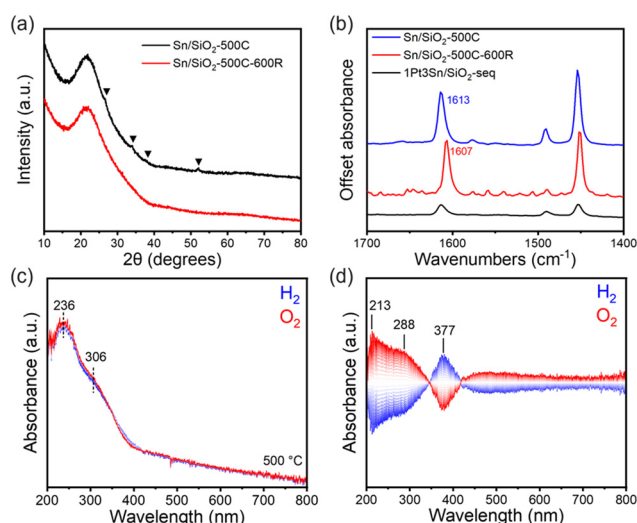

**Fig. 1** Characterizations of Sn/SiO<sub>2</sub>. (a) XRD of Sn/SiO<sub>2</sub>; (b) FTIR of pyridine adsorbed on Sn/SiO<sub>2</sub>-500C, Sn/SiO<sub>2</sub>-500C-600R, and 1Pt3Sn/SiO<sub>2</sub>-seq. Band intensities are normalized to the feature bands of SiO<sub>2</sub> (2104–1730 cm<sup>−1</sup>). (c) MES DR UV-vis of Sn/SiO<sub>2</sub> at 500 °C, original spectra during alternating O<sub>2</sub>–H<sub>2</sub> feed; (d) phase domain UV-vis spectra after phase-sensitive detection (PSD) analysis. Gas feed: 10% O<sub>2</sub>/Ar or 10% H<sub>2</sub>/Ar, total 50 sccm gas flow. Modulation frequency = 1/120 Hz (period = 120 s).



bands at  $1613\text{ cm}^{-1}$  ( $\nu_{8a}$ ),  $1491\text{ cm}^{-1}$  ( $\text{PyH}^+$  and coordinatively bound pyridine), and  $1454\text{ cm}^{-1}$  ( $\nu_{19b}$ ), characteristic of Lewis acid sites, likely originating from the Lewis acidic  $\text{Sn}^{4+}$  species.<sup>24,33,34</sup> Reduction of  $\text{Sn}/\text{SiO}_2$  does not alter the intensity of the band but leads to a red shift of the  $1613\text{ cm}^{-1}$  band to  $1607\text{ cm}^{-1}$ , attributed to the reduction of  $\text{Sn}^{4+}$  to  $\text{Sn}^{2+}$ , resulting in a decrease in the Lewis acid strength of the Sn sites.<sup>26,35</sup> This observation aligns with previous studies indicating the reduction of isolated  $\text{Sn}^{4+}$  to  $\text{Sn}^{2+}$  on  $\text{Sn}/\text{SiO}_2$  at  $500\text{ }^\circ\text{C}$ .<sup>26</sup> Therefore,  $\text{SnO}_2$  clusters are unlikely to be present under PDH reaction conditions due to their instability in a reductive atmosphere.

DR UV-vis spectra further confirmed the structure of  $\text{Sn}/\text{SiO}_2$ .<sup>24,36–38</sup> The spectra were collected at  $500\text{ }^\circ\text{C}$  in alternating  $\text{H}_2$  and  $\text{O}_2$  atmospheres (Fig. 1c). A main absorption band at  $236\text{ nm}$  can be assigned to tetrahedral Sn sites.<sup>36–38</sup> A weak shoulder around  $306\text{ nm}$ , extending beyond  $350\text{ nm}$ , is attributed to  $\text{SnO}_2$ , which has a Rutile structure consisting of a mixture of corner and edge-sharing  $\text{SnO}_6$  octahedra.<sup>38,39</sup>

Interestingly, alternating the gas feed between  $\text{H}_2$  and  $\text{O}_2$  at  $500\text{ }^\circ\text{C}$  induces reversible changes in the UV-vis spectra (Fig. 1c, top). Phase domain spectra (Fig. 1d) reveal changes in characteristic bands at  $213\text{ nm}$ ,  $288\text{ nm}$ , and  $377\text{ nm}$ . The bands at  $213\text{ nm}$  and  $288\text{ nm}$  exhibit the same phase (Fig. S4†) and can be related to the redox behavior of the tetrahedral  $\text{Sn}^{4+}$  and the  $\text{SnO}_2$  clusters, respectively, as per previous peak assignments. Upon switching from  $\text{O}_2$  to  $\text{H}_2$ , the intensities of the  $213\text{ nm}$  and  $288\text{ nm}$  bands decrease while the  $377\text{ nm}$  band increases, suggesting the reduction of  $\text{Sn}^{4+}$  species into forms (discussed below) represented by the  $377\text{ nm}$  band.<sup>40</sup>

The UV-vis band at  $377\text{ nm}$ , previously unreported in the literature, likely corresponds to the formation of  $\text{Sn}^{2+}\text{-OH}$


through the reduction of  $\text{Sn}^{4+}$ . This inference is supported by its intensification upon switching from  $\text{O}_2$  to  $\text{H}_2$ . To further investigate this, we conducted MES-DRIFTS, a technique more sensitive to  $\text{-OH}$  species. In Fig. 2a and S5a†, under alternating  $\text{H}_2$  and  $\text{O}_2$  feeds, the  $\text{SiO}_2$  support shows minor changes, with an almost flat profile between  $4000$  and  $1500\text{ cm}^{-1}$ . The perturbations observed in the  $\text{-OH}$  vibration region ( $3745$  and  $3735\text{ cm}^{-1}$ ) may arise from the reversible formation of hydrogen bonds upon introducing hydrogen.<sup>41,42</sup> Gas switching on  $\text{Pt}/\text{SiO}_2$  induces band variation at  $2042\text{ cm}^{-1}$  in Fig. S5b† due to Pt-hydride formation.<sup>43</sup> Little change is observed in the  $\text{O-H}$  region (Fig. 2b), suggesting that  $\text{H}_2$  prefers to interact with Pt rather than  $\text{-OH}$  when Pt nanoparticles are present.

On the other hand, significant changes are observed in Sn-containing samples. In Fig. S5c†, a broad and intensive background shift between  $3636\text{ cm}^{-1}$  and  $2000\text{ cm}^{-1}$  is present for  $\text{Sn}/\text{SiO}_2$ , absent in  $\text{SiO}_2$  (Fig. S5a†). This background shift likely originates from Sn species, indicating a strong interaction between Sn and the  $\text{SiO}_2$  support, resulting in a wide-range background alteration. A similar background shift, albeit with weaker intensity, is observed for  $1\text{Pt}3\text{Sn}/\text{SiO}_2\text{-seq}$  (Fig. S5d†), extending only to  $3636\text{ cm}^{-1}$ , suggesting less Sn species in direct contact with  $\text{SiO}_2$  compared to  $\text{Sn}/\text{SiO}_2$ . In the  $\text{O-H}$  vibration region of  $\text{Sn}/\text{SiO}_2$  (Fig. 2c), besides changes in isolated silanol groups at  $3744\text{ cm}^{-1}$ , perturbations are also observed at slightly lower wavenumbers between  $3739$  and  $3636\text{ cm}^{-1}$ . These changes also exist in  $1\text{Pt}3\text{Sn}/\text{SiO}_2\text{-seq}$  (Fig. 2d), but not in  $\text{SiO}_2$  (Fig. 2a) and  $\text{Pt}/\text{SiO}_2$  (Fig. 2b), indicating their association with Sn species. This is likely due to the formation and removal of  $\text{Sn-OH}$  in  $\text{H}_2$  and  $\text{O}_2$  atmospheres, previously reported around  $3665\text{ cm}^{-1}$ .<sup>24,44</sup> This agrees with the UV-vis band changes at  $377\text{ nm}$  in Fig. 1d.

Based on the spectroscopic results, Sn in  $1\text{Pt}3\text{Sn}/\text{SiO}_2\text{-seq}$  is partially alloyed with Pt, whereas Sn alone exhibits a strong interaction with the  $\text{SiO}_2$  support, forming  $\text{Sn}^{2+}\text{-OH}$  species under a reducing environment. This dynamic behavior of the PtSn catalyst under alternating gas environments provides valuable insights into the relative location of Pt and Sn species in the catalyst.


### 3.2 Pt-Sn interactions in $\text{PtSn}/\text{SiO}_2\text{-seq}$ and $\text{PtSn}/\text{SiO}_2\text{-co}$

The impregnation of Pt on  $\text{Sn}/\text{SiO}_2$  followed by subsequent reduction at  $600\text{ }^\circ\text{C}$  leads to a significantly lower pyridine band area (Fig. 1b) indicating interactions between the Pt precursor with Sn sites during impregnation and the persistence of isolated Sn sites on  $\text{SiO}_2$ . This is likely due to the preferential adsorption of  $[\text{PtCl}_6]^{2-}$  ions on the Lewis acidic  $\text{Sn}^{4+}$  sites, driven by electrostatic interactions.<sup>45</sup> Upon reduction, part of the surface  $\text{Sn}^{4+}$  is incorporated into the Pt nanoparticles, forming a PtSn alloy. Pt loadings were kept constant across all samples, while Sn loadings were varied. In Fig. 3a, XRD of  $\text{Pt}/\text{SiO}_2$  shows fcc Pt(111) diffraction pattern at  $39.801^\circ$ , consistent with standard Pt structure (PDF 03-065-

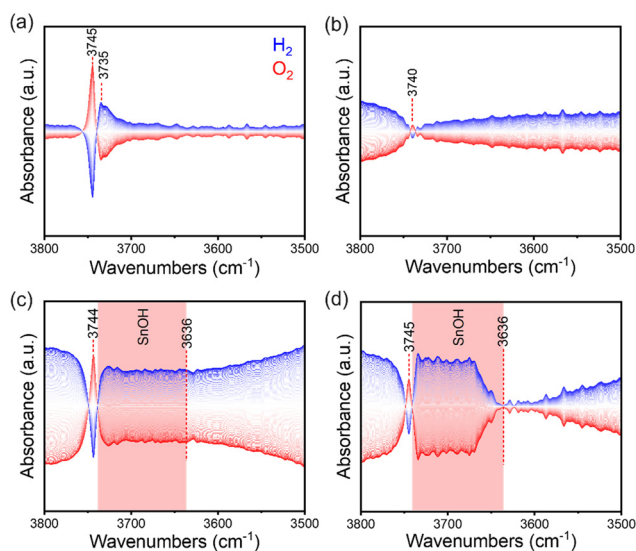

**Fig. 2** Phase domain MES-DRIFTS-FTIR in  $\text{O-H}$  vibration region for: (a)  $\text{SiO}_2$ ; (b)  $\text{Pt}/\text{SiO}_2$ ; (c)  $\text{Sn}/\text{SiO}_2$ ; and (d)  $1\text{Pt}3\text{Sn}/\text{SiO}_2\text{-seq}$ . Gas feed: 10%  $\text{O}_2/\text{Ar}$  or 10%  $\text{H}_2/\text{Ar}$ , total 50 sccm gas flow. Modulation frequency =  $1/120\text{ Hz}$  (period = 120 s). Temperature:  $400\text{ }^\circ\text{C}$ . All figures have the same y-scale.



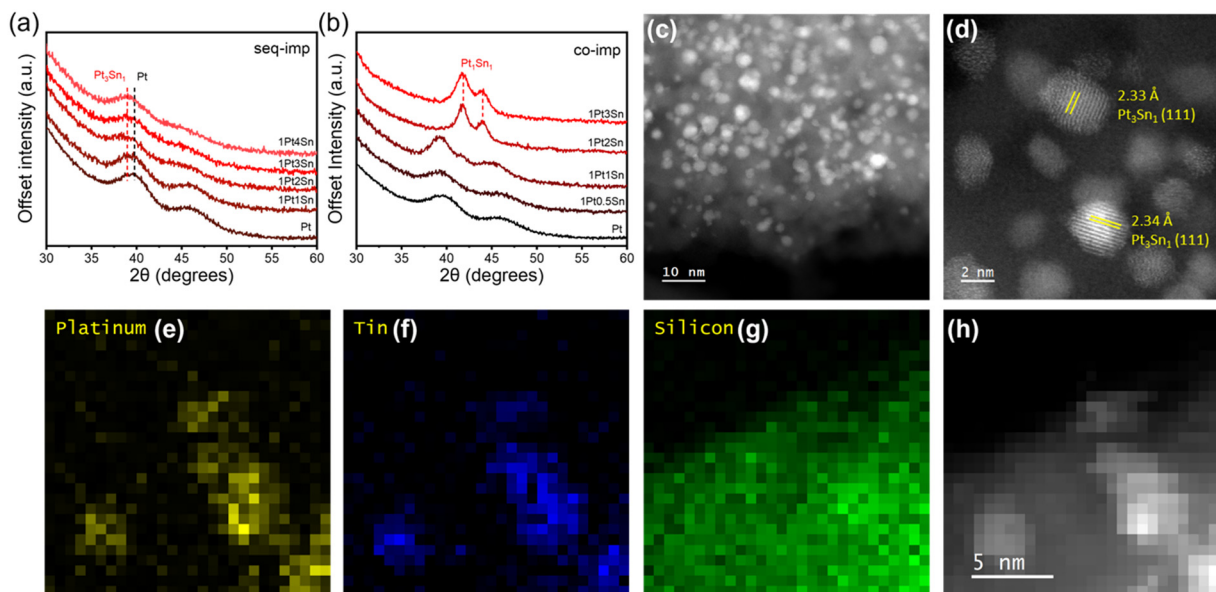


**Fig. 3** Structural characterizations of PtSn/SiO<sub>2</sub>. (a) XRD of PtSn/SiO<sub>2</sub>-seq with varying Pt:Sn ratios; (b) XRD of PtSn/SiO<sub>2</sub>-co with varying Pt:Sn ratios; (c and d) HAADF-STEM of 1Pt3Sn/SiO<sub>2</sub>-seq; (e–h) EDS mapping of 1Pt3Sn/SiO<sub>2</sub>-seq.

2868). XRD of the sequentially impregnated PtSn/SiO<sub>2</sub> with increasing Sn:Pt ratio shows a continuous shift of the Pt(111) pattern toward lower angles, suggesting the incorporation of Sn into Pt and the resulting expansion of Pt lattice.<sup>10,15</sup> The broadening of the Pt(111) pattern with increasing Sn:Pt ratio suggests random incorporation of Sn, yielding Pt–Sn nanoparticles with a distribution of Sn:Pt ratios that systematically shifts with increasing Sn:Pt ratio. Despite increasing the Sn:Pt ratio to 4:1, no Pt<sub>3</sub>Sn<sub>1</sub> intermetallic phase was detected in XRD. HAADF-STEM images show particles with an average size of 2.10 nm (Fig. 3c and S8†). HRTEM images show particles with a lattice spacing of 2.33–2.34 Å, consistent with a Pt<sub>3</sub>Sn<sub>1</sub> intermetallic phase and the XRD results. This suggests Sn species on the SiO<sub>2</sub> support not alloyed with Pt, consistent with the spectroscopic findings in the previous section. EDS mappings (Fig. 3e–h) show an almost overlapping distribution of Pt and Sn elements on SiO<sub>2</sub> support, confirming alloy formation.

For comparison, PtSn/SiO<sub>2</sub> with comparable Pt and Sn loadings were also synthesized by co-impregnation. Sn and Pt precursors were pre-mixed before one-step impregnation. Upon mixing the Pt and Sn precursor solutions, the Pt precursor changed color from a bright yellow to dark brown, suggesting the formation of Pt–Sn complexes.<sup>19,21,46–48</sup> This ensures the molecular-level mixing between Pt and Sn. In Fig. 3b, Pt<sub>3</sub>Sn<sub>1</sub> intermetallic phase starts forming in the 1Pt1Sn/SiO<sub>2</sub>-co sample. Further increase in the Sn amount led to the disappearance of Pt and Pt<sub>3</sub>Sn<sub>1</sub> patterns, leaving only the Pt<sub>1</sub>Sn<sub>1</sub> phase. This contrasts with PtSn/SiO<sub>2</sub>-seq, where no Pt<sub>3</sub>Sn<sub>1</sub> phase was observed, indicating a higher degree of alloying for co-impregnated samples. Additionally, the particle sizes of co-impregnated samples are much less uniform than sequentially impregnated ones, especially for high Sn-loading samples (Fig. S6†). This suggests that the

metal complex–support interaction during the impregnation phase is weakened in co-impregnation, likely due to the formation of Pt–Sn complexes.<sup>46,48</sup> After calcination and reduction of co-impregnated samples, the resulting catalysts have much broader particle size distributions and complicated phase compositions (Fig. S7†). Overall, PtSn/SiO<sub>2</sub>-seq samples show the most uniform particle size distribution across the whole composition range. Therefore, direct reduction was used for all catalyst synthesis.

*In situ* CO-DRIFTS provides valuable insights into the surface properties of PtSn catalysts. Fig. 4 shows the CO

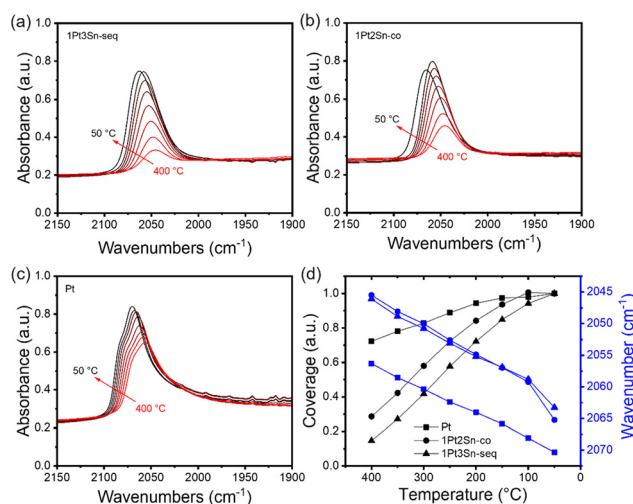

**Fig. 4** Temperature-programmed *in situ* CO-DRIFTS. (a) 1Pt3Sn/SiO<sub>2</sub>-seq; (b) 1Pt2Sn/SiO<sub>2</sub>-co; (c) Pt/SiO<sub>2</sub>; (d) comparison of temperature versus peak area and peak center location. Band area obtained by integration of 2120–1960 cm<sup>-1</sup>. Samples are reduced in 10% H<sub>2</sub> at 600 °C for 30 min, then ramped to 400 °C, and switched to 10% H<sub>2</sub>, 1% CO cofeed. Spectra collected during further ramp-down every 50 °C.



adsorption on three samples: 1Pt3Sn/SiO<sub>2</sub>-seq, 1Pt2Sn/SiO<sub>2</sub>-co, and Pt/SiO<sub>2</sub>. Sn-containing samples exhibit a lower CO stretching frequency than Pt/SiO<sub>2</sub> at all temperatures. This phenomenon can be attributed to the electronic effect of Sn on Pt, weakening CO adsorption on the Sn-modified Pt surface.<sup>49–51</sup> Interestingly, the 1Pt3Sn/SiO<sub>2</sub>-seq and 1Pt2Sn/SiO<sub>2</sub>-co show almost the same CO stretching frequencies despite different Sn loadings and synthesis methods, suggesting similar catalytic surface structures. Beyond band position, peak shapes also differ: in Fig. 4c, Pt/SiO<sub>2</sub> displays a main peak with a shoulder at higher wavenumbers, assigned to the high-Miller-index step or corner and terrace sites on Pt nanoparticles, respectively.<sup>52,53</sup> In contrast, Sn-containing samples show a single band with no shoulder at higher wavenumbers. This hints at Sn blocking the low coordination step sites, and partially covering Pt particles, resulting in smaller Pt ensembles, as reported in the literature.<sup>1,50,54</sup> Fig. 4d depicts increasing CO coverages as the temperature decreases. The relative coverage increases substantially more for Sn-containing samples than Pt/SiO<sub>2</sub>, indicating stronger CO adsorption on pure Pt surface than Sn-containing Pt surface. As the temperature drops from 100 °C to 50 °C, the coverage on 1Pt3Sn/SiO<sub>2</sub>-seq continues to increase, while it decreases slightly for 1Pt2Sn/SiO<sub>2</sub>-co. This suggests that the Sn-rich 1Pt2Sn/SiO<sub>2</sub>-co nanoparticles may undergo surface segregation of Sn below 100 °C.<sup>50</sup> Consequently, the catalyst surface structure may markedly differ at low temperatures compared to working conditions, underscoring the importance of examining the catalyst under working conditions.


### 3.3 Structural dynamics of PtSn catalyst under working conditions using *in situ* XAS and NAP-XPS

*In situ* XAS reveals the Pt–Sn interaction of the bulk catalyst during reduction. Fig. 5a displays the temperature-dependent Pt L<sub>III</sub>-edge XANES spectra of 1Pt3Sn/SiO<sub>2</sub>-seq in 5% H<sub>2</sub>. As the sample is heated from 100 °C to 200 °C, contrary to the typical downward shift in edge energy and white line energy during reduction,<sup>55,56</sup> both edge energy and white line energy shift upward by about 1 eV. This energy shift has been associated with Pt interaction with Sn, caused by electron donation from Sn to Pt,<sup>56,57</sup> suggesting an increase in Pt–Sn alloying during reduction. The white line intensity reflects the vacancy population of Pt 5d orbital.<sup>56</sup> With increasing temperature, the Pt L<sub>III</sub> white line intensity slightly decreases, as shown in the inset of Fig. 5a. This is likely due to further alloying and a stronger electron donation from Sn. In the Fourier-transformed R space EXAFS spectra in Fig. 5b, no peak is present at ~1.7 Å corresponding to Pt–O, suggesting a reduced Pt state at as low as 100 °C.<sup>15,58</sup> The peak shapes are similar to those reported in the literature, suggesting the coexistence of Pt and PtSn phases.<sup>56,58,59</sup>

Fig. 5c shows the Sn K-edge XANES spectra during the initial ramp-up of the reduction. The series of spectra exhibit 5 isosbestic points marked by the arrows (see Fig. S9†), indicating that the spectra are a linear combination of two principal components.<sup>60</sup> The SnO<sub>2</sub> standard (red dotted line) shares all 5 isosbestic points with the sample spectra, suggesting that a SnO<sub>2</sub>-like phase is one of the two components across all Pt–Sn catalysts. Conversely, Sn<sup>0</sup> fails to capture the second isosbestic point, suggesting that the second component may have a slightly different structure than pure Sn<sup>0</sup>, likely influenced by Pt alloying. The white line intensity in Fig. 5c decreases rapidly as the sample is ramped from room temperature to 200 °C. At the same time, a minor change occurs at higher temperatures, suggesting that Sn species are predominantly reduced below 200 °C.


Fig. 5d shows Sn K-edge EXAFS spectra. The fresh 1Pt3Sn/SiO<sub>2</sub>-seq sample measured at room temperature (blue line) shows strong Sn–O scattering at 1.52 Å, indicating that Sn in the air-exposed fresh catalyst is mostly oxidized. The radial distance is slightly lower than 1.60 Å of SnO<sub>2</sub> (red dotted line) in Fig. 5d), suggesting that Sn is tetrahedrally rather than octahedrally coordinated with O as in bulk SnO<sub>2</sub>.<sup>61,62</sup> Despite exposure to air, 1Pt3Sn/SiO<sub>2</sub>-seq lacks Sn–Sn scattering between 2.5 Å and 4 Å, which is prominent in bulk SnO<sub>2</sub>, indicating that the Sn species, although oxidized, are highly dispersed, consistent with our XRD and TEM characterizations in previous sections. As the reduction temperature rises, the intensity of Sn–O scattering between 1.5 Å and 2.0 Å decreases and shifts towards higher radial distances, as shown in Fig. 5d inset. These shifts are clear indications of the continuous Sn reduction.

XPS provides surface properties of the fresh catalysts (Fig. 6 and S10†). The calcined Sn/SiO<sub>2</sub> has an initial Sn:Si atomic ratio of 0.0080, close to 0.0078 of 1Pt3Sn/SiO<sub>2</sub>-seq,

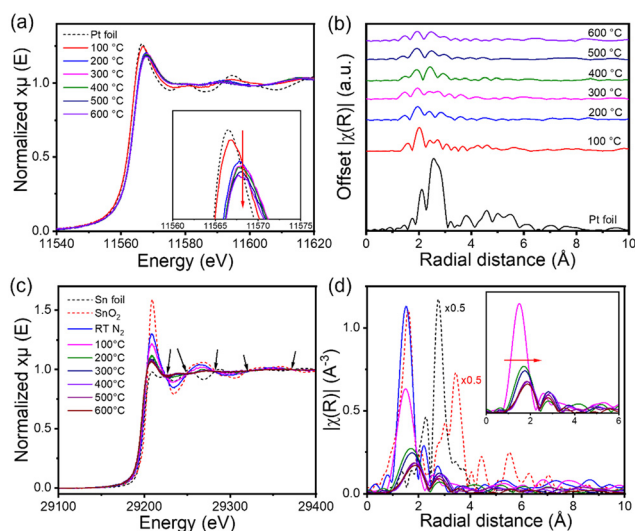

**Fig. 5** *In situ* XAS of 1Pt3Sn/SiO<sub>2</sub>-seq. (a) Pt L<sub>III</sub>-edge XANES spectra, inset: zoom in view of white line region; (b) Fourier transform of the Pt L<sub>III</sub>-edge EXAFS spectra; (c) Sn K-edge XANES spectra, isosbestic points indicated by the arrows; (d) Fourier transforms of the Sn K-edge EXAFS spectra, inset: zoom in view of 0–6 Å region, standard samples' intensities are multiplied by 0.5. Reduction condition: 5% H<sub>2</sub>/N<sub>2</sub>, 20 sccm total flow.



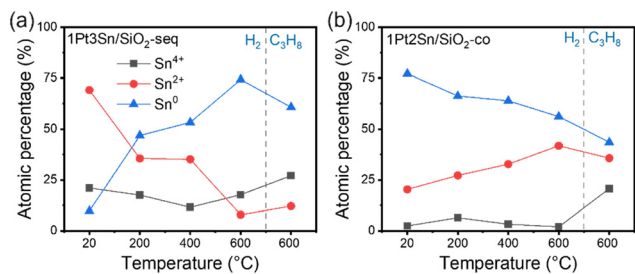

**Fig. 6** NAP-XPS surface Sn oxidation states composition evolution with temperature. (a) 1Pt3Sn/SiO<sub>2</sub>-seq; (b) 1Pt2Sn/SiO<sub>2</sub>-co. Measurement conducted 1 mbar H<sub>2</sub> or C<sub>3</sub>H<sub>8</sub> at indicated temperatures. Samples are heated up to 600 °C in H<sub>2</sub> then switched to C<sub>3</sub>H<sub>8</sub> atmosphere at 600 °C. Original spectra in Fig. S8†

indicating that the impregnation of Pt and subsequent reduction in H<sub>2</sub> did not significantly affect the Sn dispersion on the SiO<sub>2</sub> support. This suggests that most Sn remains close to the SiO<sub>2</sub> support, while a small amount may get alloyed with Pt. XRD results in Fig. 3a also suggest a low degree of alloying in the sequentially impregnated samples, confirming this observation.

In contrast, 1Pt2Sn/SiO<sub>2</sub>-co has a Sn:Si ratio of 0.0032, suggesting a lower Sn dispersion. This aligns with the TEM results in Fig. S6,† as well as the low Pt:Si ratio of 0.0025, compared to 0.0051 of 1Pt3Sn/SiO<sub>2</sub>-seq, confirming larger metal particles in co-impregnated samples. The data suggests that Sn species tend to alloy with Pt rather than disperse on SiO<sub>2</sub>, consistent with the XRD results in Fig. 3b.

Apart from surface atomic ratios, the Sn oxidation states of the fresh catalysts also provide insight into the degree of alloying between Sn and Pt. Sn 3d<sub>5/2</sub> core level peak of Sn/SiO<sub>2</sub> centers around 488.6 eV, indicative of Sn<sup>4+</sup> species, while 1Pt3Sn/SiO<sub>2</sub>-seq centers around 486.6 eV, and 1Pt2Sn/SiO<sub>2</sub>-co around 486.0 eV. The shift toward lower binding energy after Pt impregnation suggests that the Sn species in 1Pt3Sn/SiO<sub>2</sub>-seq and 1Pt2Sn/SiO<sub>2</sub>-co are more reduced, likely due to the partial alloying with Pt.

Next, samples were heated to 600 °C in 1 mbar H<sub>2</sub> to assess the surface Sn oxidation state evolution. In Fig. S11,† Sn/SiO<sub>2</sub> contains mostly Sn<sup>4+</sup> species (81%). As the temperature rises, the fraction of Sn<sup>4+</sup> in Sn/SiO<sub>2</sub> decreases rapidly while Sn<sup>0</sup> and Sn<sup>2+</sup> increase. In the literature, bulk SnO<sub>2</sub> is typically reduced above 500 °C.<sup>26,28,30,63</sup> It is noteworthy that, in our case, surface reduction happens at a much lower temperature. The initial Sn<sup>4+</sup> species are likely highly dispersed oligomers and are reduced more easily than bulk SnO<sub>2</sub>, forming Sn–OH species mentioned in the UV-vis and FTIR results. Additionally, the copper plate used to hold the sample may facilitate the dissociation of H<sub>2</sub> and, thereby, the reduction of Sn species due to the small sample thickness on the copper plate.

The Pt-containing samples in Fig. 6 show a lower Sn<sup>4+</sup> percentage before reduction, suggesting a smaller amount of Sn<sup>4+</sup> species on the SiO<sub>2</sub> support. 1Pt2Sn/SiO<sub>2</sub>-co contains 2% Sn<sup>4+</sup> and 77% Sn<sup>0</sup> prior to reduction, indicating considerable


alloying between Sn and Pt. Furthermore, the Sn<sup>4+</sup> percentages remain relatively constant during reduction for both PtSn samples, suggesting that these Sn<sup>4+</sup> species are most likely isolated and have strong interaction with the support, making them difficult to reduce with H<sub>2</sub>.

With the rising temperature, 1Pt3Sn/SiO<sub>2</sub>-seq shows a decreasing Sn<sup>2+</sup> percentage and an increasing Sn<sup>0</sup> percentage, which follows the reduction process. However, 1Pt2Sn/SiO<sub>2</sub>-co shows the opposite trend: while the percentages of Sn<sup>2+</sup> and Sn<sup>0</sup> remain relatively constant, a slight increase in Sn<sup>2+</sup> and a decrease in Sn<sup>0</sup> are observed. This hints at a distinct structure of these samples despite a similar Pt and Sn content. It is likely that as the temperature increases, the Sn species in the Sn-rich 1Pt2Sn/SiO<sub>2</sub>-co nanoparticles becomes mobile and interacts with SiO<sub>2</sub> at the periphery of the alloy nanoparticles, increasing the apparent oxidation states measured at the sample surface. Meanwhile, on 1Pt3Sn/SiO<sub>2</sub>-seq, Pt-rich nanoparticles facilitate H<sub>2</sub> dissociation and assist the reduction and incorporation of the neighboring Sn species.

### 3.4 Propane dehydrogenation over PtSn/SiO<sub>2</sub>

It is known that adding Sn promotes the stability of PDH Pt catalysts. Fig. 7a illustrates the time-on-stream conversion of PtSn/SiO<sub>2</sub>-seq catalysts with various Sn loadings. Pt/SiO<sub>2</sub> shows high initial activity but quickly deactivates in the first 10 min, with selectivity toward C<sub>3</sub>H<sub>6</sub> also dropping significantly, likely due to the increasing relative contribution from gas phase cracking as the catalyst deactivates. Increased Sn loading maximizes the activity at a 1:3 Pt:Sn ratio for sequentially impregnated samples and a 1:2 ratio for co-impregnated samples.

To better understand the optimal surface configuration, we estimate the surface site densities and Pt:Sn atomic

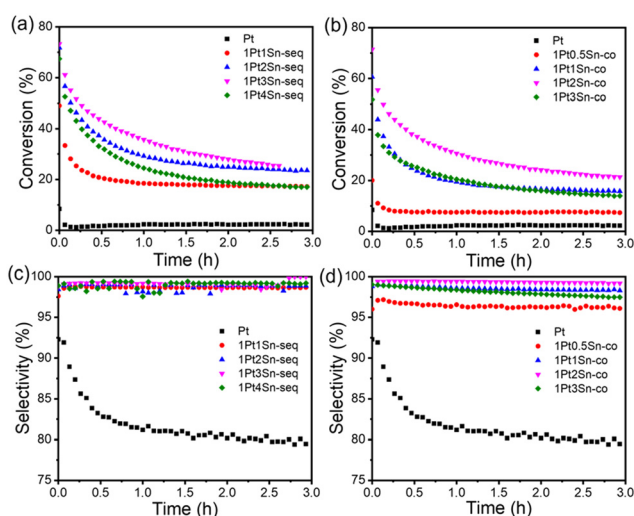

**Fig. 7** PDH activity of PtSn/SiO<sub>2</sub> catalysts. (a) Conversion vs. time of PtSn/SiO<sub>2</sub>-seq; (b) conversion vs. time of PtSn/SiO<sub>2</sub>-co; (c) selectivity vs. time of PtSn/SiO<sub>2</sub>-seq; (d) selectivity vs. time of PtSn/SiO<sub>2</sub>-co. Reaction condition: 600 °C, 50 mg catalyst, 5% C<sub>3</sub>H<sub>8</sub>/He, 54.2 sccm total flow. Equilibrium conversion at 600 °C: 88.5%.



**Table 1** Quantitative comparison of Pt site densities, turnover frequencies (TOF), and XPS surface atomic ratios. DRIFTS CO band areas are normalized by the signal of the SiO<sub>2</sub> support (2108 cm<sup>-1</sup>, 1729 cm<sup>-1</sup>). Sn/SiO<sub>2</sub> was calcined at 500 °C and reduced at 600 °C before measurement at room temperature in UHV. XPS of other samples are collected at 400 °C in 1 mbar H<sub>2</sub> atmosphere. Note that the inelastic mean free paths of photoelectrons are similar to the particle sizes, and therefore, the XPS results cannot be used to determine the exact composition of the surface layers of the nanoparticles

Sample	CO chemisorption (μmol g <sup>-1</sup> )	Normalized DRIFTS CO area (a.u.)	Pt site density (μmol g <sup>-1</sup> )	TOF (s <sup>-1</sup> )	XPS Pt:Sn ratio	XPS Pt:Si ratio	XPS Sn:Si ratio
Pt/SiO <sub>2</sub>	38.61	0.3859	38.61	—	—	0.0038	—
1Pt3Sn/SiO <sub>2</sub> -seq	—	0.3054	30.55	0.89	0.79	0.0056	0.0071
1Pt2Sn/SiO <sub>2</sub> -co	—	0.3177	31.78	0.83	1.34	0.0063	0.0028
Sn/SiO <sub>2</sub>	—	—	—	—	—	—	0.0093

ratios in Table 1. For Pt/SiO<sub>2</sub>, the Pt site density (from pulse CO chemisorption) is 38.61 μmol g<sup>-1</sup>, and the Pt loading (from ICP analysis) is 1.63 wt%, resulting in a dispersion of 46.18% and a mean particle diameter of 2.39 nm, consistent with the 2.47 nm average size from HRTEM (Fig. S12†). CO chemisorption does not work for the Sn-containing samples due to the surface segregation of Sn at low temperatures.<sup>15,64</sup> Instead, we estimate their Pt site densities from the CO band areas in DRIFTS. The Pt site densities and TOF for 1Pt3Sn/SiO<sub>2</sub>-seq and 1Pt2Sn/SiO<sub>2</sub>-co are summarized in Table 1. Despite the distinct synthesis procedures, bulk compositions (Fig. 3a and b), and particle sizes, these samples have comparable surface site density, TOF, and deactivation profile. Upon reduction, the nanoparticle surfaces likely self-adjust to a specific surface Pt:Sn ratio with similar active sites. The comparable DRIFTS CO frequencies of both Sn-containing samples at all temperatures in Fig. 4d also corroborate this point, as the CO frequency typically changes with the surface Pt:Sn ratio due to the electron donation from Sn to Pt.<sup>1,49</sup>

Based on the XRD result in Fig. 3b, 1Pt2Sn/SiO<sub>2</sub>-co contains Pt<sub>1</sub>Sn<sub>1</sub> phase in the bulk. Further increase of Sn amount results in a similar XRD pattern, suggesting that a Sn:Pt ratio higher than one does not alter the Pt<sub>1</sub>Sn<sub>1</sub> pattern of the diffraction result. Therefore, the bulk of the nanoparticles 1Pt2Sn/SiO<sub>2</sub>-co have a composition of Pt<sub>1</sub>Sn<sub>x</sub> ( $x \geq 1$ ). However, its XPS surface Pt:Sn ratio is above 1, suggesting surface Pt enrichment compared with the bulk. Additionally, during NAP-XPS in H<sub>2</sub>, the initial Pt:Sn ratio of the sample before reduction is 1.17, slightly lower than that measured during reduction, suggesting that a reductive environment could pull Pt to the surface driven by the chemical potential of H<sub>2</sub>.

On the other hand, the Pt(111) diffraction pattern of 1Pt3Sn/SiO<sub>2</sub>-seq is between that of Pt and Pt<sub>3</sub>Sn<sub>1</sub> (Fig. 3a), indicating a bulk composition of Pt<sub>3</sub>Sn<sub>x</sub> ( $x < 1$ ). However, its XPS surface Pt:Sn ratio is below 1. This is understandable because much of the Sn species in 1Pt3Sn/SiO<sub>2</sub>-seq is on the support rather than in the metal particles, and XPS only gives the total surface composition, including the surface of the support and surface of the nanoparticles. Indeed, the XPS Sn:Si ratio of 1Pt3Sn/SiO<sub>2</sub>-seq is just slightly lower than Sn/SiO<sub>2</sub>, suggesting that most of the Sn species remain on the support after Pt addition, in direct contrast with 1Pt2Sn/SiO<sub>2</sub>-co, whose XPS Sn:Si ratio is significantly lower than Sn/SiO<sub>2</sub>.

Therefore, despite the low XPS Pt:Sn ratio in 1Pt3Sn/SiO<sub>2</sub>-seq, the nanoparticle surface can still be Pt-rich and likely similar to that of 1Pt2Sn/SiO<sub>2</sub>-co due to their similar reactivity and CO DRIFTS results.

The discrepancy in compositions from different techniques highlights the concentration gradient from the nanoparticle bulk to the surface. While the final surface compositions for both samples are similar, 1Pt2Sn/SiO<sub>2</sub>-co features a Sn-rich core and Pt-rich surface, driven by the chemical potential of reductive atmospheres; whereas 1Pt3Sn/SiO<sub>2</sub>-seq features a Pt-rich core and Sn-rich surface, driven by the high Sn concentration at the support surface and the metal-support interface.

Based on the above analysis, the optimal surface Pt-Sn composition for PDH can be estimated. Co-impregnated samples show an increasing trend of TOF to a synthesis Sn:Pt ratio of 2.0 (Fig. S13†). Despite being a surface-sensitive technique, XPS still provides information from deeper than a few atomic layers near the surface. Therefore, the optimal surface Pt:Sn ratio can be slightly higher than 1.34 of 1Pt2Sn/SiO<sub>2</sub>-co. On the other hand, it cannot be higher than the ratio for the bulk of 1Pt3Sn/SiO<sub>2</sub>-seq, estimated to be 6.2 from XRD result based on Vegard's law.<sup>65,66</sup> Therefore, a surface with  $1.34 < \text{Pt:Sn} < 6.2$  is optimal, indicating that a Pt-rich surface is essential for high PDH performance.

## 4 Conclusions

The PtSn/SiO<sub>2</sub> catalyst is complex due to the various species present and its dynamic structure upon exposure to different temperatures and atmospheres. In this work, we synthesized the PtSn/SiO<sub>2</sub> catalyst using different procedures and Pt:Sn ratios. Sequential impregnation generates separated Pt and Sn, while co-impregnation generates highly alloyed PtSn nanoparticles. The PDH activity is maximum at a 1:3 Pt:Sn ratio for the sequentially impregnated sample and a 1:2 ratio for the co-impregnated sample. Through *in situ* UV-vis and DRIFTS, we discovered that in addition to the reduction of Sn in alloy nanoparticles, Sn<sup>4+</sup> species on SiO<sub>2</sub> also get reduced, forming Sn<sup>2+</sup>-OH species in H<sub>2</sub> at 500 °C. By *in situ* surface-sensitive techniques, such as XPS and CO DRIFTS, the surfaces of 1Pt3Sn/SiO<sub>2</sub>-seq and 1Pt2Sn/SiO<sub>2</sub>-co are alike and possess similar catalytic properties despite the distinct synthesis and bulk structure. In 1Pt2Sn/SiO<sub>2</sub>-co, Sn atoms



migrate from the Sn-rich nanoparticles to the PtSn-support interface. In contrast, in 1Pt3Sn/SiO<sub>2</sub>-seq, Sn species close to the Pt-rich nanoparticles tend to get reduced and incorporated into them. The opposite Pt-Sn concentration gradient in co-impregnated and sequentially-impregnated samples highlights the effect of synthesis procedures on the surface structure and the need for a Pt-rich surface for optimal PDH activity and stability. This study focused on the dynamics during catalyst reduction. To obtain a full picture, the catalyst dynamics during regeneration is also worth investigating in future work.

## Data availability

The data supporting this article have been included as part of the ESI.† The MES spectroscopic data were analyzed with software developed by our group, available on GitHub at <https://github.com/worradal/wavey>.

## Author contributions

Kewei Yu: methodology, investigation, data collection, writing – original draft; Matthew Scarpelli: data collection, investigation; Sagar Sourav: methodology, investigation, formal analysis, editing; Alfred Worrad: methodology, formal analysis, software; J. Anibal Boscoboinik: resources, methodology; Lu Ma, Steven N. Ehrlich, Nebojsa Marinkovic: resources, methodology; Weiqing Zheng: conceptualization, supervision, writing – review & editing; Dionisios G. Vlachos: conceptualization, resources, supervision, funding acquisition, writing – review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the National Science Foundation's "Designing Materials to Revolutionize and Engineer our Future" (DMREF) program under Award Number 2323700. This work was partly carried out at the Singh Center for Nanotechnology, supported by the NSF National Nanotechnology Coordinated Infrastructure Program under grant NNCI-2025608. *Ex situ* X-ray photoelectron spectroscopy conducted at the University of Delaware was sponsored by the National Science Foundation, Major Research Instrumentation, Award Number: CHE-1428149. This research used the Near ambient X-ray photoelectron spectroscopy of the Center for Functional Nanomaterials (CFN), a U.S. Department of Energy (DOE) Office of Science User Facility at Brookhaven National Laboratory under Contract No. DE-SC0012704. This research also used the 7-BM QAS beamline X-ray absorption spectroscopy of the National Synchrotron Light Source II, a U.S. DOE Office of Science User Facility operated by the Brookhaven National Laboratory under Contract No. DE-SC0012704.

## References

- 1 J. J. H. B. Sattler, J. Ruiz-Martinez, E. Santillan-Jimenez and B. M. Weckhuysen, *Chem. Rev.*, 2014, **114**, 10613–10653.
- 2 Z.-P. Hu, D. Yang, Z. Wang and Z.-Y. Yuan, *Chin. J. Catal.*, 2019, **40**, 1233–1254.
- 3 C. Li and G. Wang, *Chem. Soc. Rev.*, 2021, **50**, 4359–4381.
- 4 N. S. Zadeh and S. Talebi, *Shale Gas - New Aspects and Technologies*, 2018, DOI: [10.5772/intechopen.76542](https://doi.org/10.5772/intechopen.76542).
- 5 S. Chen, X. Chang, G. Sun, T. Zhang, Y. Xu, Y. Wang, C. Pei and J. Gong, *Chem. Soc. Rev.*, 2021, **50**, 3315–3354.
- 6 M. Martino, E. Meloni, G. Festa and V. Palma, *Catalysts*, 2021, **11**, 1070.
- 7 M. Farsi, A. Jahanmiri and M. R. Rahimpour, *Asia-Pac. J. Chem. Eng.*, 2013, **8**, 862–869.
- 8 C. DiGiulio, *Overview of Honeywell UOP Oleflex™ in 2018 Spring AIChE Meeting*, 2018.
- 9 Y. Liu, X. Zong, A. Patra, S. Caratzoulas and D. G. Vlachos, *ACS Catal.*, 2023, **13**, 2802–2812.
- 10 D. Y. DeSario and F. J. DiSalvo, *Chem. Mater.*, 2014, **26**, 2750–2757.
- 11 V. Grolier and R. Schmid-Fetzer, *J. Alloys Compd.*, 2008, **450**, 264–271.
- 12 C. Ye, M. Peng, Y. Wang, N. Zhang, D. Wang, M. Jiao and J. T. Miller, *ACS Appl. Mater. Interfaces*, 2020, **12**, 25903–25909.
- 13 L. Liu, M. Lopez-Haro, C. W. Lopes, S. Rojas-Buzo, P. Concepcion, R. Manzorro, L. Simonelli, A. Sattler, P. Serna, J. J. Calvino and A. Corma, *Nat. Catal.*, 2020, **3**, 628–638.
- 14 H. Wan, L. Qian, N. Gong, H. Hou, X. Dou, L. Zheng, L. Zhang and L. Liu, *ACS Catal.*, 2023, **13**, 7383–7394.
- 15 L. Deng, H. Miura, T. Shishido, S. Hosokawa, K. Teramura and T. Tanaka, *ChemCatChem*, 2014, **6**, 2680–2691.
- 16 C. Xu, S. Tan, Y. Tang, S. Xi, B. Yao, A. Wade, B. Zhao, S. Lu, Y. Du, M. Tian, C. He, L. Ma, X. Fu, J. Shi, J. Lu, A. G. R. Howe, S. Dai, G. Luo and Q. He, *Appl. Catal., B*, 2024, **341**, 123285.
- 17 J. Wang, X. Chang, S. Chen, G. Sun, X. Zhou, E. Vovk, Y. Yang, W. Deng, Z.-J. Zhao, R. Mu, C. Pei and J. Gong, *ACS Catal.*, 2021, **11**, 4401–4410.
- 18 Y. Xing, L. Kang, J. Ma, Q. Jiang, Y. Su, S. Zhang, X. Xu, L. Li, A. Wang, Z.-P. Liu, S. Ma, X. Y. Liu and T. Zhang, *Chin. J. Catal.*, 2023, **48**, 164–174.
- 19 A. H. Motagamwala, R. Almallahi, J. Wortman, V. O. Igenegbai and S. Linic, *Science*, 2021, **373**, 217–222.
- 20 B. S. Patil, P. D. Srinivasan, E. Atchison, H. Zhu and J. J. Bravo-Suárez, *React. Chem. Eng.*, 2019, **4**, 667–678.
- 21 N. Kaylor and R. J. Davis, *J. Catal.*, 2018, **367**, 181–193.
- 22 L. Deng, H. Miura, T. Shishido, Z. Wang, S. Hosokawa, K. Teramura and T. Tanaka, *J. Catal.*, 2018, **365**, 277–291.
- 23 H. Zhu, D. H. Anjum, Q. Wang, E. Abou-Hamad, L. Emsley, H. Dong, P. Laveille, L. Li, A. K. Samal and J.-M. Basset, *J. Catal.*, 2014, **320**, 52–62.
- 24 P. Ferrini, J. Dijkmans, R. De Clercq, S. Van de Vyver, M. Dusselier, P. A. Jacobs and B. F. Sels, *Coord. Chem. Rev.*, 2017, **343**, 220–255.



- 25 C. Hammond, S. Conrad and I. Hermans, *Angew. Chem., Int. Ed.*, 2012, **51**, 11736–11739.
- 26 H. Wang, H. Huang, K. Bashir and C. Li, *Appl. Catal., A*, 2020, **590**, 117291.
- 27 Y. N. Palai, A. Shrotri, M. Asakawa and A. Fukuoka, *Catal. Today*, 2021, **365**, 241–248.
- 28 Y. Yue, J. Fu, C. Wang, P. Yuan, X. Bao, Z. Xie, J.-M. Basset and H. Zhu, *J. Catal.*, 2021, **395**, 155–167.
- 29 B.-S. Kim, J. Lee, H.-S. Yoon and S.-K. Kim, *Mater. Trans.*, 2011, **52**, 1814–1817.
- 30 F. Lan, X. Wang, X. Xu, R. Zhang and N. Zhang, *React. Kinet., Mech. Catal.*, 2012, **106**, 113–125.
- 31 M. L. Colaiaanni, P. J. Chen, J. T. Yates and M. Arbab, *Appl. Surf. Sci.*, 1993, **68**, 467–475.
- 32 T. Ma, S. Wang, M. Chen, R. V. Maligal-Ganesh, L.-L. Wang, D. D. Johnson, M. J. Kramer, W. Huang and L. Zhou, *Chem*, 2019, **5**, 1235–1247.
- 33 M. Tamura, K. Shimizu and A. Satsuma, *Appl. Catal., A*, 2012, **433–434**, 135–145.
- 34 M. E. Z. Velthoen, S. Nab and B. M. Weckhuysen, *Phys. Chem. Chem. Phys.*, 2018, **20**, 21647–21659.
- 35 G. Busca, *Phys. Chem. Chem. Phys.*, 1999, **1**, 723–736.
- 36 S. Roy, K. Bakhtmutsky, E. Mahmoud, R. F. Lobo and R. J. Gorte, *ACS Catal.*, 2013, **3**, 573–580.
- 37 R. Bermejo-Deval, R. Gounder and M. E. Davis, *ACS Catal.*, 2012, **2**, 2705–2713.
- 38 W. Dai, Q. Lei, G. Wu, N. Guan, M. Hunger and L. Li, *ACS Catal.*, 2020, **10**, 14135–14146.
- 39 J. A. Toledo-Antonio, R. Gutiérrez-Baez, P. J. Sebastian and A. Vázquez, *J. Solid State Chem.*, 2003, **174**, 241–248.
- 40 C.-M. Fan, Y. Peng, Q. Zhu, L. Lin, R.-X. Wang and A.-W. Xu, *J. Phys. Chem. C*, 2013, **117**, 24157–24166.
- 41 B. A. Morrow and A. J. McFarlan, *J. Phys. Chem.*, 1992, **96**, 1395–1400.
- 42 R. S. McDonald, *J. Phys. Chem.*, 1958, **62**, 11.
- 43 A. I. Serykh, O. P. Tkachenko, V. Y. Borovkov, V. B. Kazansky, M. Beneke, N. I. Jaeger and G. Schulz-Ekloff, *Phys. Chem. Chem. Phys.*, 2000, **2**, 5647–5652.
- 44 P. Fink, B. Camara, E. Welz and P. D. Ty, *Z. Chem.*, 1971, **11**, 473–474.
- 45 K. P. de Jong, *Synthesis of Solid Catalysts*, John Wiley & Sons, 2009.
- 46 G. T. Baronetti, S. R. de Miguel, O. A. Scelza, M. A. Fritzler and A. A. Castro, *Appl. Catal.*, 1985, **19**, 77–85.
- 47 N. Prakash, M.-H. Lee, S. Yoon and K.-D. Jung, *Catal. Today*, 2017, **293–294**, 33–41.
- 48 J. F. Young, R. D. Gillard and G. Wilkinson, *J. Chem. Soc.*, 1964, 5176–5189.
- 49 Q. Wang, D. Tichit, F. Meunier and H. Guesmi, *J. Phys. Chem. C*, 2020, **124**, 9979–9989.
- 50 A. Moscu, Y. Schuurman, L. Veyre, C. Thieuleux and F. Meunier, *Chem. Commun.*, 2014, **50**, 8590–8592.
- 51 K. Balakrishnan and J. Schwank, *J. Catal.*, 1992, **138**, 491–499.
- 52 M. J. Lundwall, S. M. McClure and D. W. Goodman, *J. Phys. Chem. C*, 2010, **114**, 7904–7912.
- 53 D. M. Haaland, *Surf. Sci.*, 1987, **185**, 1–14.
- 54 R. D. Cortright and J. A. Dumesic, *J. Catal.*, 1994, **148**, 771–778.
- 55 D. Eggart, X. Huang, A. Zimina, J. Yang, Y. Pan, X. Pan and J.-D. Grunwaldt, *ACS Catal.*, 2022, **12**, 3897–3908.
- 56 Y. Uemura, Y. Inada, K. K. Bando, T. Sasaki, N. Kamiuchi, K. Eguchi, A. Yagishita, M. Nomura, M. Tada and Y. Iwasawa, *Phys. Chem. Chem. Phys.*, 2011, **13**, 15833–15844.
- 57 J. H. Kim, S. M. Choi, S. H. Nam, M. H. Seo, S. H. Choi and W. B. Kim, *Appl. Catal., B*, 2008, **82**, 89–102.
- 58 G. J. Siri, J. M. Ramallo-López, M. L. Casella, J. L. G. Fierro, F. G. Requejo and O. A. Ferretti, *Appl. Catal., A*, 2005, **278**, 239–249.
- 59 A. Borgna, S. M. Staggs and D. E. Resasco, *J. Phys. Chem. B*, 1998, **102**, 5077–5081.
- 60 S. Calvin, *XAFS for Everyone*, CRC Press, 2013.
- 61 S. R. Bare, S. D. Kelly, W. Sinkler, J. J. Low, F. S. Modica, S. Valencia, A. Corma and L. T. Nemeth, *J. Am. Chem. Soc.*, 2005, **127**, 12924–12932.
- 62 C. Hammond, D. Padovan, A. Al-Nayili, P. P. Wells, E. K. Gibson and N. Dimitratos, *ChemCatChem*, 2015, **7**, 3322–3331.
- 63 M. Haneda, Y. Ota, Y. Doi and M. Hattori, *J. Mater. Sci.*, 2016, **51**, 10949–10959.
- 64 L. Deng, X. Liu, Z. Wu, J. Xu, Z. Zhou and M. Xu, *Catal. Lett.*, 2023, **153**, 3665–3677.
- 65 A. R. Denton and N. W. Ashcroft, *Phys. Rev. A: At., Mol., Opt. Phys.*, 1991, **43**, 3161–3164.
- 66 E. Antolini, F. Colmati and E. R. Gonzalez, *J. Power Sources*, 2009, **193**, 555–561.

