

Cite this: *Mater. Adv.*, 2024,  
5, 3965Received 26th November 2023,  
Accepted 17th March 2024

DOI: 10.1039/d3ma01052j

rsc.li/materials-advances

# The introduction of gallium ions into V<sub>2</sub>O<sub>5</sub> interlayers for highly reversible Zn ion batteries

Ming Zhao,<sup>a</sup> Shilong Li,<sup>a</sup> Xiang Wu<sup>ib</sup>\*<sup>a</sup> and Abdukayum Abdukader<sup>ib</sup>\*<sup>b</sup>

It is very important to construct energy storage systems with high safety and excellent electrochemical performance. In particular, aqueous Zn ion batteries (AZIBs) possess the characteristics of low-cost and environmental benignity. However, there are few cathode materials that match well with the zinc anode. Herein, Ga<sup>3+</sup> pre-intercalation into V<sub>2</sub>O<sub>5</sub> layers promotes the insertion/extraction kinetics of zinc ions. The assembled Zn/V<sub>2</sub>O<sub>5</sub>-0.1Ga battery with 3 M Zn(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub> electrolyte shows a specific capacity of 512.07 mA h g<sup>-1</sup> at a current density of 0.1 A g<sup>-1</sup>. It delivers an energy density of 281.64 W h kg<sup>-1</sup> at a power density of 55 W kg<sup>-1</sup>. It can also provide a reversible capacity of 110 mA h g<sup>-1</sup> at 10 A g<sup>-1</sup> with a retention rate of 91.43% after 5000 cycles, revealing its potential applications in future energy storage devices.

## 1. Introduction

In the past few years, the excessive depletion of fossil fuels has caused a serious energy crisis and environmental pollution. It is necessary to design and develop many sustainable energy sources.<sup>1–4</sup> Among them, Li-ion batteries (LIBs) have been utilized in smartphones, electric vehicles and laptops. Nevertheless, their future development is still restricted considering the high cost and toxic organic electrolyte.<sup>5,6</sup> Thus, it is crucial to seek an alternative to LIBs, such as rechargeable aqueous multivalent ion batteries (Na, K, Ca, Zn, and Mg).<sup>7–10</sup> Aqueous zinc ion batteries (AZIBs) attract wide attention owing to their high theoretical capacity (820 mA h g<sup>-1</sup>), and the abundant resources and low redox potential of Zn<sup>2+</sup>/Zn (−0.76 V vs. SHE).<sup>11–13</sup> However, it is still an urgent task to explore suitable cathode materials, such as Prussian blue analogues, and Mn-based and vanadium-based materials.<sup>14,15</sup> Prussian blue analogues show low capacity and short cycle life.<sup>16</sup> Manganese-based materials still need to be improved owing to low rate performance and unstable structures.<sup>17,18</sup>

Recently, various V<sub>2</sub>O<sub>5</sub> structures have been widely investigated as cathode materials for AZIBs,<sup>19</sup> owing to their diverse oxidation states (V<sup>2+</sup>, V<sup>3+</sup>, V<sup>4+</sup>, and V<sup>5+</sup>) and unique crystal features.<sup>20,21</sup> The crystal structure of V<sub>2</sub>O<sub>5</sub> connects the distorted VO<sub>5</sub> square cones through the shared edges and corners to form a 2D layered structure with weak van der Waals

interactions between the layers. For instance, Chen *et al.* prepared V<sub>2</sub>O<sub>5</sub> samples supported on carbon cloth by a template route. The fabricated cells delivered a capacity of 370 mA h g<sup>-1</sup> at 0.2 A g<sup>-1</sup>.<sup>22</sup> The Zn/V<sub>2</sub>O<sub>5</sub>@CNT devices presented a capacity of 485.8 at 0.1 A g<sup>-1</sup>.<sup>23</sup> However, the capacity of the reported V<sub>2</sub>O<sub>5</sub> electrode materials is far from their theoretical capacity (589 mA h g<sup>-1</sup>). The strong electrostatic repulsion between the zinc ions and the host structure results in a slow electrochemical kinetic behavior. Therefore, some strategies have been proposed to modify the cathode material of AZIBs, such as metal ion pre-embedding, defect engineering and coating of other materials.

Metal ion pre-embedding is thought to be an efficient strategy to enhance the electrochemical performance of AZIBs. Many metal cations have been introduced into target materials, such as Zn, K, and Ca. Zhang *et al.* introduced La<sup>3+</sup> into a layered V<sub>2</sub>O<sub>5</sub> structure. The assembled device shows a capacity of 405 mA h g<sup>-1</sup> at 0.1 A g<sup>-1</sup> and energy density of 227.5 W h kg<sup>-1</sup> at 55 W kg<sup>-1</sup>.<sup>24</sup> The Zn/V<sub>2</sub>O<sub>5</sub> cells deliver a discharge capacity of 350 mA h g<sup>-1</sup> at 0.1 A g<sup>-1</sup> by the intercalation of PANI.<sup>25</sup> Liu and coworkers used K<sup>+</sup> ions as a structure pillar for introduction into V<sub>2</sub>O<sub>5</sub> interlayers. The resulting material possessed a capacity of 479.8 mA h g<sup>-1</sup> at 0.2 A g<sup>-1</sup> and maintained 91.3% of its initial capacity at 10 A g<sup>-1</sup> after 3000 cycles.<sup>26</sup>

In this work, we prepare Ga<sup>3+</sup>-intercalated V<sub>2</sub>O<sub>5</sub> nanobelts by a simple hydrothermal route. Gallium possesses natural advantages, such as its strong electronegativity forming stable chemical bonds. It has a small radius compared to other cations, making it easier to approach the target sample. The introduction of metal ions promotes the transfer of Zn ions, and maintains structural stability of the electrode materials. A series of zinc ion batteries are assembled using the obtained

<sup>a</sup> School of Materials Science and Engineering, Shenyang University of Technology, Shenyang 110870, P. R. China. E-mail: wuxiang05@sut.edu.cn

<sup>b</sup> Xinjiang Key Laboratory of Novel Functional Materials Chemistry, College of Chemistry and Environmental Sciences, Kashi University, Kashi 844000, P. R. China. E-mail: abdukadere@sina.com



$V_2O_5-0.1Ga$  samples as cathodes. The cells deliver a discharge capacity of  $512.07 \text{ mA h g}^{-1}$  at  $0.1 \text{ A g}^{-1}$ . They maintain 91.43% of the original capacity at  $10 \text{ A g}^{-1}$  after 5000 cycles. The batteries present an energy density of  $281.64 \text{ W h kg}^{-1}$  at a power density of  $55 \text{ W kg}^{-1}$ . This work provides new ideas in designing cathode materials that match well with Zn anodes.

## 2. Experimental section

All the purchased chemicals were used without any purification. Typically, 4 mmol  $V_2O_5$  (Alfa Aesar) powder was dissolved into 50 mL of de-ionized water and stirred for 30 min at  $50 \text{ }^\circ\text{C}$ . Then, 1 mL of 30%  $H_2O_2$  was added into the above solution. After that, a certain amount of HCl (Codow) solution is uniformly dispersed into the above mixture to adjust the pH to 1. Subsequently, 0.1 mmol  $Ga(NO_3)_3 \cdot xH_2O$  (Macklin) was added into the prepared solution with stirring for half an hour. Then, the solution was placed into an 80 mL Teflon-lined stainless-steel autoclave and maintained at  $180 \text{ }^\circ\text{C}$  for 48 h. After cooling to room temperature, the solution was washed with alcohol and deionized water several times and dried under vacuum at  $60 \text{ }^\circ\text{C}$  for 12 h. For comparison, different amounts of  $Ga(NO_3)_3 \cdot xH_2O$  (0, 0.05, and 0.2 mmol) were also added to similar solutions and the prepared samples were labeled as  $V_2O_5$ ,  $V_2O_5-0.05Ga$ , and  $V_2O_5-0.2Ga$ , respectively.

### 2.1. Structural characterization

The crystallographic information of the as-prepared samples was characterized by powder X-ray diffraction (XRD, 7000, Shimadzu, Cu K $\alpha$  radiation,  $\lambda = 0.1541 \text{ nm}$ , 40 kV), scanning

electron microscopy (SEM, Gemini 300-71-31), and X-ray photoelectron spectroscopy (XPS, Thermo Kalpha). The specific surface area was studied by the Brunauer–Emmett–Teller (BET, Micromeritics ASAP, JW-TB200) method.

### 2.2. Electrochemical measurements

The cathode materials consist of the active materials, carbon black (Power Origin Limited) and polyvinylidene fluoride (Power Origin Limited) with a mass ratio of 7:2:1. Then a certain amount of *N*-methyl-*L*-2-pyrrolidone (Damao) was added to form a slurry, which was evenly pressed onto graphite paper. A piece of zinc foil was used as the anode with a thickness of 0.2 mm. The coin cells (CR2032) were assembled by using 3 M  $Zn(CF_3SO_3)_2$  (Bidepharm) as the electrolyte. The average loading mass of the cathode is about 1.5 mg. The galvanostatic intermittent titration technique (GITT), galvanic charge–discharge (GCD) analysis and cycling stability tests were performed at a voltage range of 0.4–1.5 V using a Neware battery tester (CT-4008T-5V6A-164). The CV curves and Nyquist plots of the cells were measured by using an electrochemical workstation (Shanghai Chenhua, CHI660E).

## 3. Results and discussion

First, the crystal structures of the samples are investigated by XRD, as shown in Fig. 1a. It can be observed that the diffraction peaks match well with the  $V_2O_5$  phase (PDF# 41-1426). The  $V_2O_5-0.1Ga$  sample presents sharp and strong diffraction peaks. The main peaks at  $15.30$ ,  $20.32$ ,  $21.68$ ,  $26.16$ ,  $31.04$ , and  $41.36^\circ$  belong to the (200), (001), (101), (110), (301) and

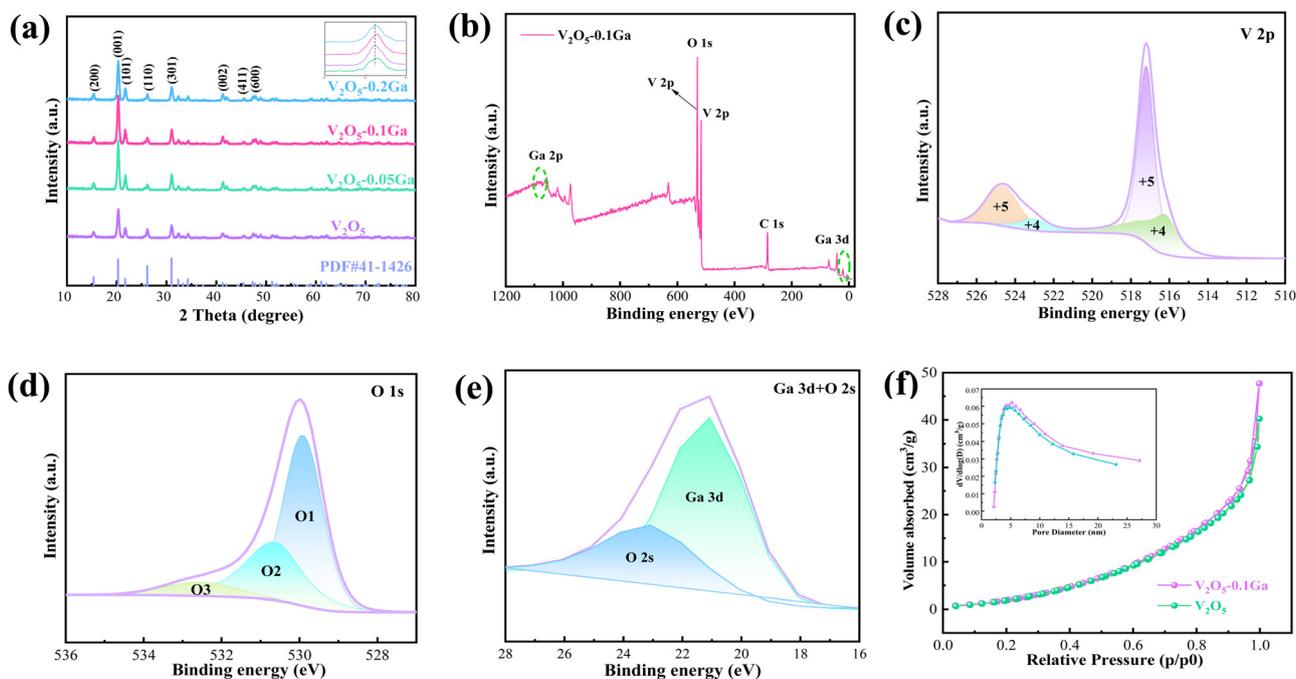


Fig. 1 Structural characterizations of the samples. (a) XRD patterns. (b) XPS survey spectrum. (c) V 2p, (d) O 1s, and (e) Ga 3d+O 2s. (f)  $N_2$  adsorption–desorption isotherms; inset represents the pore size distributions of the  $V_2O_5-0.1Ga$  products.



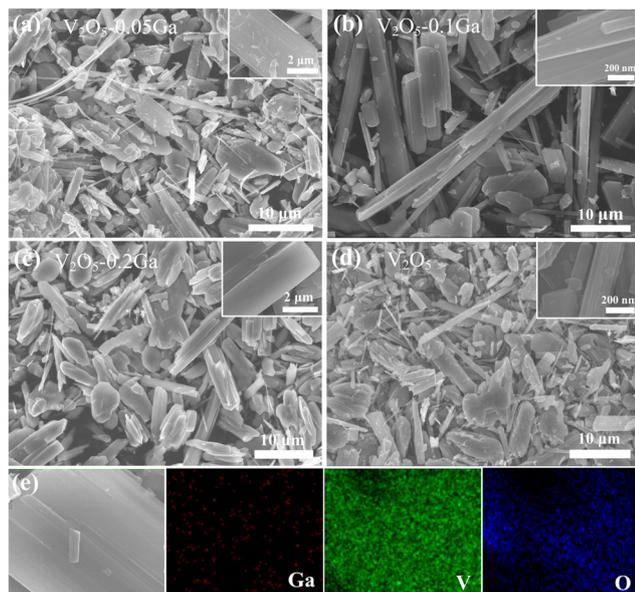


Fig. 2 SEM images of (a) V<sub>2</sub>O<sub>5</sub>-0.05Ga, (b) V<sub>2</sub>O<sub>5</sub>-0.1Ga, (c) V<sub>2</sub>O<sub>5</sub>-0.2Ga and (d) V<sub>2</sub>O<sub>5</sub> samples. (e) The corresponding elemental mapping of the V<sub>2</sub>O<sub>5</sub>-0.1Ga samples.

(002) crystal planes, respectively. By enlarging the XRD pattern, it can be observed that the (101) crystal plane shifts to the right. This demonstrates the successful doping of Ga ions into the V<sub>2</sub>O<sub>5</sub> host structure. The lattice parameters  $a = 11.516 \text{ \AA}$ ,  $b = 3.566 \text{ \AA}$ , and  $c = 4.373 \text{ \AA}$ . Then XPS is used to investigate the valence states and elemental composition of the electrode materials. Fig. 1b presents the full spectrum of the V<sub>2</sub>O<sub>5</sub>-0.1Ga sample, revealing the existence of the V, O, Ga and C

elements. From Fig. 1c, the binding energies at 516.28/523.08 eV and 517.18/524.78 eV are in accordance with V<sup>4+</sup> and V<sup>5+</sup>.<sup>27</sup> According to previous reports, V<sub>2</sub>O<sub>5</sub> samples with mixed valences (V<sup>4+</sup> and V<sup>5+</sup>) possess fast reaction kinetics and low polarization intensity.<sup>28</sup> The O 1s spectrum can be fitted into three peaks, as shown in Fig. 1d. The peaks at 529.98, 530.68 and 532.68 eV can be indexed to oxygens in the metal oxide,<sup>29</sup> V=O bonds,<sup>30</sup> and O-H from surface-absorbed water,<sup>31</sup> respectively. The Ga 3d spectrum in Fig. 1e shows the signal peak at 20.8 eV, which confirms the presence of Ga<sup>3+</sup> in the V<sub>2</sub>O<sub>5</sub> samples.<sup>32</sup> Fig. 1f shows nitrogen adsorption and desorption isotherms of the V<sub>2</sub>O<sub>5</sub> and V<sub>2</sub>O<sub>5</sub>-0.1Ga samples. The specific surface area of V<sub>2</sub>O<sub>5</sub>-0.1Ga is 27.42 m<sup>2</sup> g<sup>-1</sup>, which is larger than that of the V<sub>2</sub>O<sub>5</sub> product (24.09 m<sup>2</sup> g<sup>-1</sup>). In addition, the total pore volumes of the V<sub>2</sub>O<sub>5</sub>-0.1Ga and V<sub>2</sub>O<sub>5</sub> samples are 0.061 and 0.052 cm<sup>3</sup> g<sup>-1</sup>, respectively. The results demonstrate that the addition of Ga element can increase the specific surface area and the active sites.

SEM is then utilized to observe the morphologies of the samples. As described in Fig. 2a-d, the growth process of the V<sub>2</sub>O<sub>5</sub> samples is investigated by controlling the content of Ga<sup>3+</sup>. In Fig. 2b, the V<sub>2</sub>O<sub>5</sub>-0.1Ga electrode possesses a belt-like shape. In contrast, the other three samples show uneven microcrystals. Using V<sub>2</sub>O<sub>5</sub>-0.1Ga samples as a cathode, the exposed surface is expected to provide abundant active sites to obtain superior rate performance. As seen in Fig. 2e, the elemental mapping confirms a uniform distribution of three elements of V, O and Ga along the surface of the nanobelts, which demonstrates that Ga<sup>3+</sup> is doped into the V<sub>2</sub>O<sub>5</sub> host structure.

To study the electrochemical performance of the samples, some CR2032 coin cells are assembled with 3 M Zn(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub> as the electrolyte. Fig. 3a shows the first five cycle CV curves of the

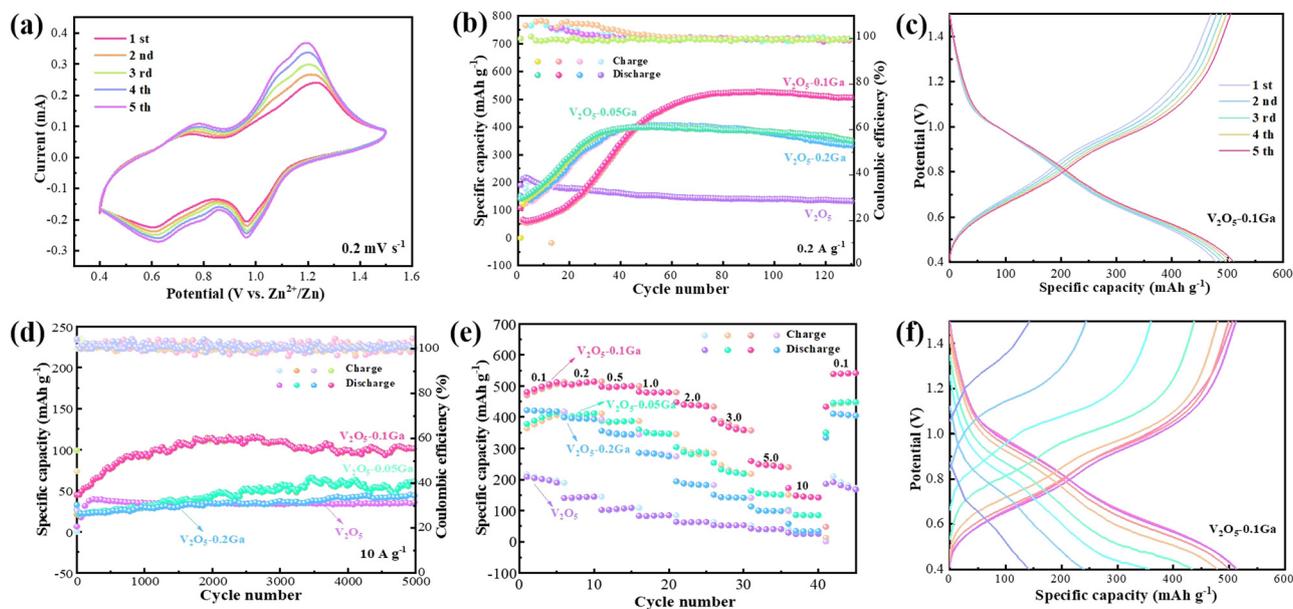


Fig. 3 Electrochemical performance. (a) CV curves in the first 5 cycles at 0.2 mV s<sup>-1</sup>, (b) cycling performance at 0.2 A g<sup>-1</sup>, (c) GCD curves of the first five cycles at 0.1 A g<sup>-1</sup>, (d) long-term cycling at 10 A g<sup>-1</sup>, (e) rate capability at different current densities and (f) GCD curves at various current densities.



Table 1 The electrochemical performance of the  $V_2O_5-0.1Ga$  electrode materials

Materials	Morphology	Current density ( $A\ g^{-1}$ )	Discharge capacity ( $mA\ h\ g^{-1}$ )	Electrolyte	Ref.
$VO_2@PPy$	Hollow spheres	0.1	440	3 M $Zn(CF_3SO_3)_2$	33
$V_2O_5$	Nanofibers	0.02	319	3 M $Zn(CF_3SO_3)_2$	34
Mn-doped- $VO_2$	Nanobelts	0.1	209.6	3 M $Zn(CF_3SO_3)_2$	35
$Ni_{0.25}V_2O_5 \cdot nH_2O$	Nanoribbons	0.2	389	3 M $ZnSO_4$	36
$VO_2 \cdot 0.2H_2O$	Nanocuboids	0.25	423	2 M $ZnSO_4$	37
$V_2O_5/PANI$	Nanosheets	0.1	400	2 M $ZnSO_4$	38
$K_{1.15}V_5O_{13} \cdot 1.3H_2O$	Nanobelts	0.2	461	3 M $Zn(OTf)_2$	39
$Ba_{1.2}V_6O_{16} \cdot 3H_2O$	Nanobelts	0.1	321	2 M $ZnSO_4$	40
$V_2O_5$	Hollow spheres	0.2	280	3.65 M $ZnSO_4$	41
$V_2O_5-0.1Ga$	Nanobelts	0.1	512.07	3 M $Zn(CF_3SO_3)_2$	This work

$V_2O_5-0.1Ga$  sample at  $0.2\ mV\ s^{-1}$ . The curves maintain the same shapes well, indicating their high reversibility of the redox reactions. Furthermore, there are two pairs of redox peaks located at 1.19/0.96 V and 0.77/0.62 V, which are related to the multi-step intercalation/de-intercalation of  $Zn^{2+}$ . Fig. 3b presents the cycling stability of the samples. After many cycles of activation, the discharge capacity of the  $V_2O_5-0.1Ga$  sample delivers a specific capacity of  $526.8\ mA\ h\ g^{-1}$  at  $0.2\ A\ g^{-1}$  and maintains a retention rate of 95.8% after 130 cycles. The GCD curves of the  $V_2O_5-0.1Ga$  products show several charge-discharge platforms (Fig. 3c), which are in accordance with the corresponding CV curves shown in Fig. 3a.

The cycling stability of the cells is also evaluated at  $10\ A\ g^{-1}$ , as depicted in Fig. 3d. The capacity of the  $V_2O_5-0.1Ga$  sample reaches  $110\ mA\ h\ g^{-1}$  with a retention rate of 91.43% after 5000 cycles. Fig. 3e shows the corresponding rate performance of the batteries. The discharge specific capacities of the  $V_2O_5-0.1Ga$  electrodes are 512.07, 514.03, 499.67, 479.18, 437.59, 360.66, 244.64, are  $148.40\ mA\ h\ g^{-1}$  at current densities from 0.1 to  $10\ A\ g^{-1}$ . When it returns to  $0.1\ A\ g^{-1}$ , the battery still

obtains a capacity of  $540.57\ mA\ h\ g^{-1}$ . This demonstrates that the moderate amount of  $Ga^{3+}$  is conducive to the enhancement of the specific capacity and rate capability. On the contrary, excessive  $Ga^{3+}$  incorporation may lead to the disruption of the crystal structure and volume expansion of the  $V_2O_5$  samples, thus producing adverse effects. Furthermore, the GCD curves (Fig. 3f) of the  $Zn/V_2O_5-0.1Ga$  batteries show that the capacity decreases with increasing current density. Table 1 lists the zinc-ion storage performance of several electrode materials.<sup>33-41</sup> It demonstrates the excellent electrochemical performance of  $Zn/V_2O_5-0.1Ga$  cells.

Fig. 4a presents the CV curves of the  $Zn/V_2O_5-0.1Ga$  cells at various scan rates ( $0.2-1.0\ mV\ s^{-1}$ ). With the increasing of the sweep speed, the positive and negative peak currents move to high and low potentials, respectively. The shape of the curves remains almost unchanged, showing their excellent reversibility. For the CV curves, the relationship between peak current ( $i$ ) and sweep speed ( $v$ ) can be obtained through the equation as follows:

$$i = av^b \quad (1)$$

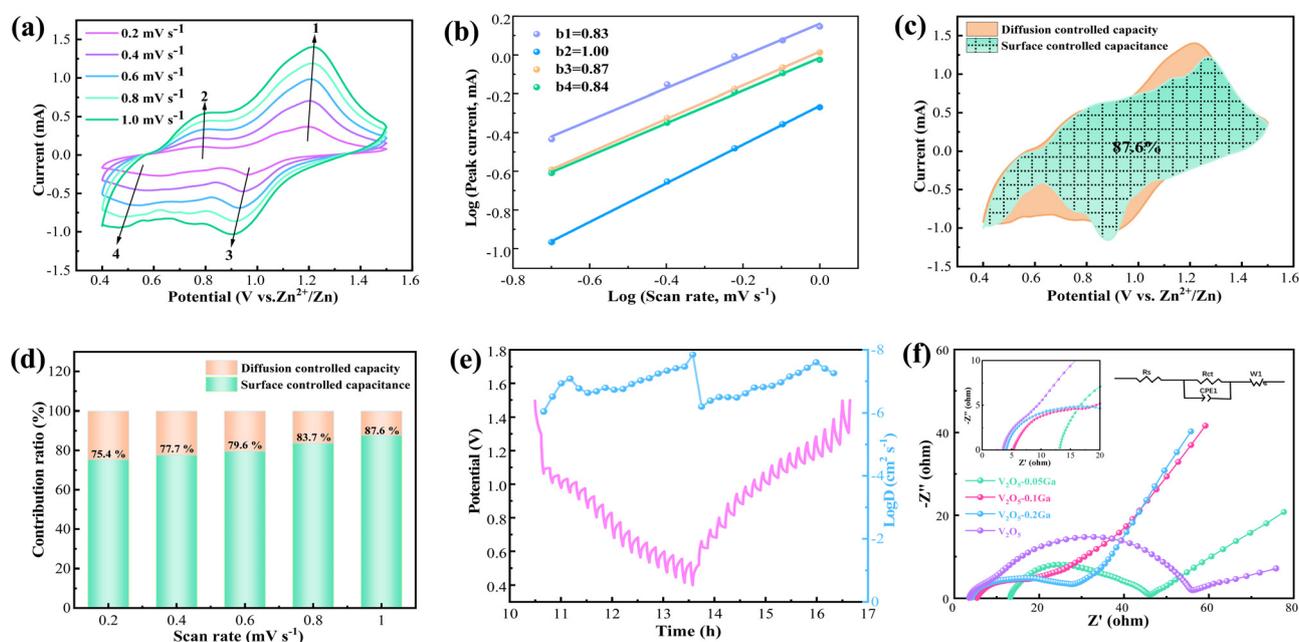


Fig. 4 Energy storage kinetics of the  $V_2O_5-0.1Ga$  electrodes for AZIBs. (a) CV curves, (b) the fitting plots of  $\log(i)$  and  $\log(v)$ , (c) and (d) the capacitive contribution ratios at various scan rates, (e) GITT curves and (f) Nyquist plots.



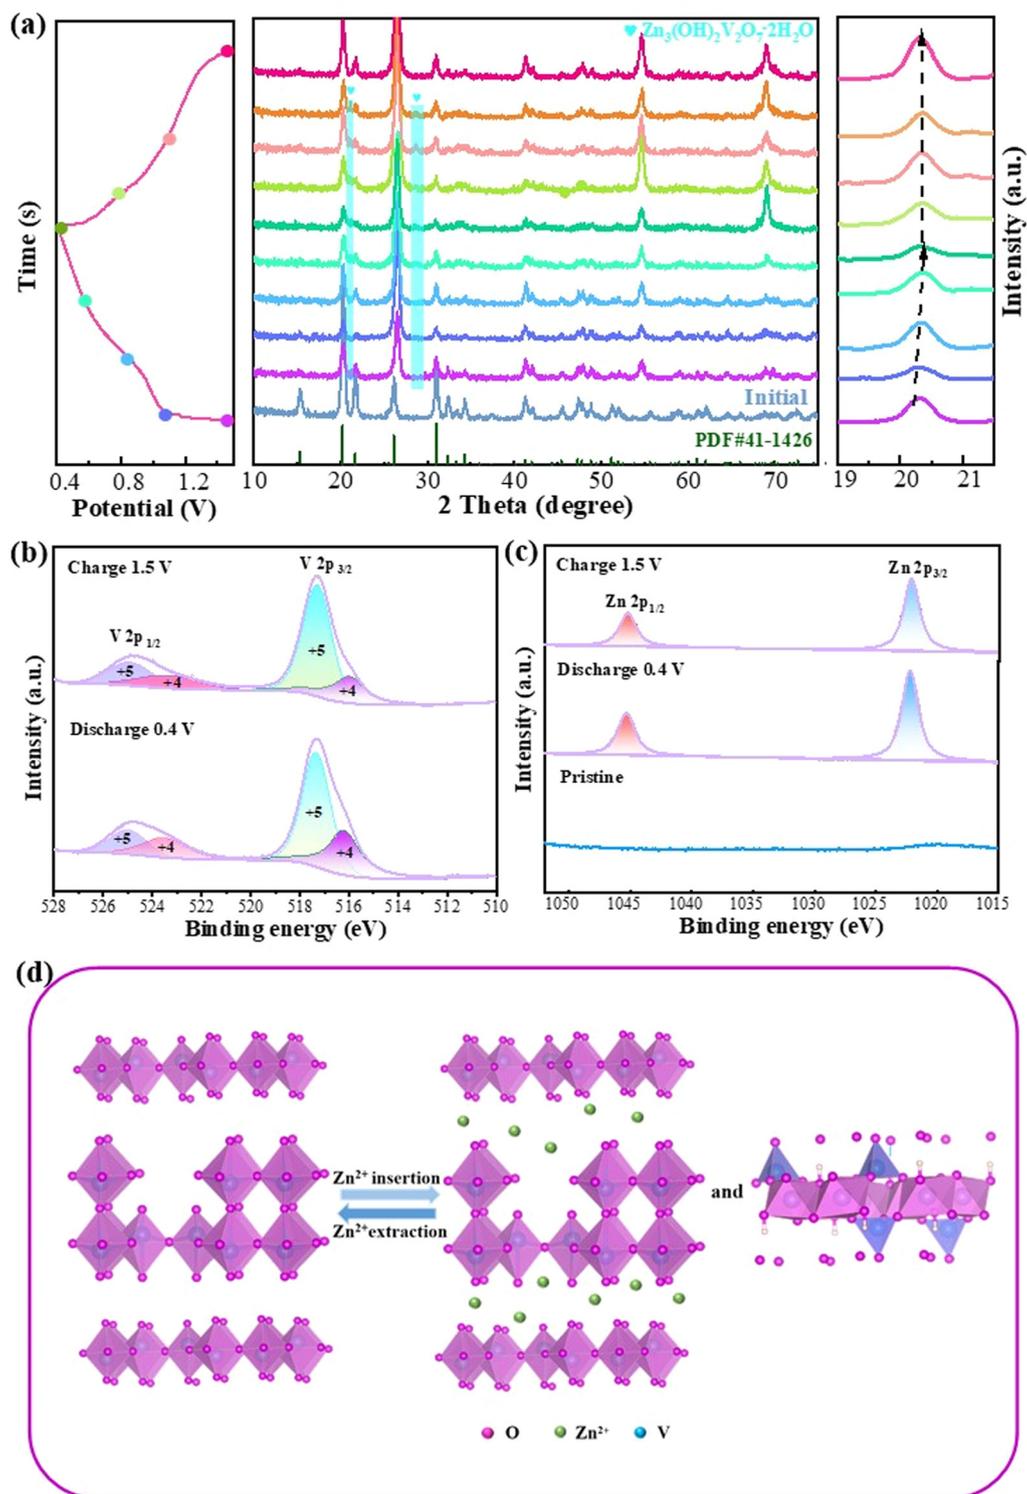


Fig. 5 Structural and morphology characterization. (a) *Ex situ* XRD patterns at various charge/discharge states, (b) and (c) XPS spectra of V and Zn elements and (d) schematic diagram of the  $\text{Zn}^{2+}$  insertion mechanism on the  $\text{V}_2\text{O}_5-0.1\text{Ga}$  cathode.

where  $a$  and  $b$  are adjustable constants. The  $b$  value can be obtained by a linear fitting. The electrochemical reaction is determined by a diffusion-controlled process when the value of  $b$  is close to 0.5, while it is capacitance-controlled behavior

if  $b \geq 1$ . If the  $b$  value is 0.5–1, it indicates a pseudocapacitive contribution- and battery behavior-dominated reaction process. From Fig. 4b, the  $b$  values are 0.83, 1.00, 0.87 and 0.84, respectively. This confirms the capacitive contribution.



In addition, the following equation can be utilized to calculate the pseudocapacitive and diffusion contributions:

$$i(V) = k_1 v + k_2 v^{1/2} \quad (2)$$

where  $k_1$  and  $k_2$  are fixed constants. The parameter  $k_1 v$  is defined as the surface-controlled process, while  $k_2 v^{1/2}$  is the diffusion-controlled one. The capacitive process reaches 87.6% of the total capacity at 1.0 mV s<sup>-1</sup> (Fig. 4c). In Fig. 4d, the capacitance contribution ratio increases from 75.4% to 87.6% with the sweep rate increasing. The GITT curves are characterized to further evaluate the diffusion ability of zinc ions. From Fig. 4e, the  $D_{\text{Zn}^{2+}}$  values of the V<sub>2</sub>O<sub>5</sub>-0.1Ga sample are determined to be 10<sup>-6</sup> and 10<sup>-8</sup> cm<sup>2</sup> s<sup>-1</sup> in the discharge state. This demonstrates that the V<sub>2</sub>O<sub>5</sub>-0.1Ga nanobelts accelerate the Zn<sup>2+</sup> migration. EIS is utilized to further investigate the zinc ion storage process in the Zn/V<sub>2</sub>O<sub>5</sub>-0.1Ga battery. The curves consist of a semicircle in the high frequency region and a straight line in the low one. The radius of the semicircle represents the charge transfer resistance ( $R_{\text{ct}}$ ) between the electrode and electrolyte. As presented in Fig. 4f, V<sub>2</sub>O<sub>5</sub>-0.1Ga samples possess a lower charge transfer resistance ( $R_{\text{ct}}$ ) than the other samples, indicating their excellent reaction kinetics. In addition, the V<sub>2</sub>O<sub>5</sub>-0.1Ga samples show an  $R_s$  value of 5.1 Ω.


The energy density and power density can be calculated based on eqn (3) and (4):

$$E = QU/2m \quad (3)$$

$$P = iU/2m \quad (4)$$

where  $E$  (W h kg<sup>-1</sup>) and  $P$  (W kg<sup>-1</sup>) refer to the energy density and power density, respectively.  $Q$  (A h) represents the discharge capacity,  $U$  (V) is the operating voltage,  $i$  (A) denotes the discharge current, and  $m$  (kg) refers to the mass of active material. Therefore, it can be concluded that the cells possess an energy density of 281.64 W h kg<sup>-1</sup> at a power density of 55 W kg<sup>-1</sup> at 0.1 A g<sup>-1</sup>.

*Ex situ* XRD was performed to study the Zn<sup>2+</sup> storage mechanism of the Zn/V<sub>2</sub>O<sub>5</sub>-0.1Ga batteries at different stages (Fig. 5a). The (001) crystal plane shifts to a high angle when the voltage drops from 1.5 V to 0.4 V. This is due to the strong electrostatic adsorption between the intercalated Zn<sup>2+</sup> and V<sub>2</sub>O<sub>5</sub> materials, which reduces the interplanar spacing of the (001) plane.<sup>42</sup> After full charging, the plane returns to its original state, which is attributed to the reversible removal of Zn<sup>2+</sup> in the host material. Besides, a new phase Zn<sub>3</sub>(OH)<sub>2</sub>V<sub>2</sub>O<sub>7</sub>·2H<sub>2</sub>O appears during the reaction due to the insertion of Zn<sup>2+</sup>, demonstrating that Zn<sup>2+</sup> is embedded successfully into the V<sub>2</sub>O<sub>5</sub>-0.1Ga samples. The generation of a new phase is related to H<sup>+</sup> in the electrolyte. The electrochemical reaction process can be represented as below:



Finally, XPS spectra are again obtained to study the composition and chemical valence of the V<sub>2</sub>O<sub>5</sub>-0.1Ga electrode during the charge and discharge states. In Fig. 5b, the V 2p<sub>1/2</sub> and V 2p<sub>3/2</sub> diffraction peaks can be attributed to V<sup>4+</sup> (523.68/516.28 eV) and V<sup>5+</sup> (524.98/517.38 eV), respectively.<sup>43</sup> In the charge state, the signal of the V<sup>4+</sup> peaks decreases, while that of V<sup>5+</sup> increases. This is caused by reversible insertion/extraction of Zn<sup>2+</sup> in the redox reactions. As seen in Fig. 5c, there are no Zn<sup>2+</sup> signals detected in the pristine state. When discharged to 0.4 V, the peaks at 1022.18 eV and 1045.38 eV belong to Zn 2p<sub>3/2</sub> and Zn 2p<sub>1/2</sub>. The peak signal is lower during charging than discharging. It is worth noting that the intensity of the Zn signal peak does not disappear completely after charging, which is due to the irreversible de-embedding of some Zn<sup>2+</sup>. Fig. 5d illustrates an electrochemical reaction schematic of the reversible insertion/extraction of Zn<sup>2+</sup>.

## 4. Conclusions

In summary, we have prepared several Ga-ion pre-embedded V<sub>2</sub>O<sub>5</sub> nanobelts by a hydrothermal strategy. The obtained samples show large specific surface areas, which is beneficial to increasing the reaction active sites. The pre-embedding of Ga<sup>3+</sup> effectively maintains the stability of the electrode material during repeated charging and discharging. The assembled Zn/V<sub>2</sub>O<sub>5</sub>-0.1Ga possesses an outstanding specific capacity and long cycle life after 5000 cycles and ultrafast Zn<sup>2+</sup> diffusion capability. Moreover, they also achieve high energy density and power density. The superior performance V<sub>2</sub>O<sub>5</sub>-0.1Ga cathode materials show great potential for advanced and safe aqueous zinc ion batteries.

## Author contributions

Ming Zhao: conceptualization, software, data curation, writing -- original draft preparation, and methodology, Shilong Li: visualization, and Xiang Wu and Abdokayum Abdokader: supervision, writing -- reviewing and editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This project is supported by the Natural Science Foundation of China (no. 52172218) and the Tianshan Innovation Team Plan of Xinjiang Uygur Autonomous Region (2023D14002).

## References

- 1 Y. Liu, Y. Liu and X. Wu, Defect engineering of vanadium-based electrode materials for zinc ion battery, *Chin. Chem. Lett.*, 2023, **34**, 107839.



- 2 S. Zhong, Y. S. Yu, Y. Yang, Y. Yao, L. F. Wang, S. N. He, Y. X. Yang, L. Liu, W. P. Sun, Y. Z. Feng, H. G. Pan, X. H. Rui and Y. Yu, Molecular engineering on solvation structure of carbonate electrolyte toward durable sodium metal battery at  $-40\text{ }^{\circ}\text{C}$ , *Angew. Chem., Int. Ed.*, 2023, **62**, e2023011693.
- 3 N. M. Tri, S. Preston, P. Andrea, F. Michael G, H. Xiao, G. Ilja and S. Ullrich, Polymer-templated mesoporous lithium titanate microspheres for high-performance lithium batteries, *Mater. Adv.*, 2022, **3**, 362–372.
- 4 Q. Xia, T. Xia and X. Wu, PPy decorated  $\alpha\text{-Fe}_2\text{O}_3$  nanosheets as flexible supercapacitor electrode, *Rare Met.*, 2022, **41**, 1195–1201.
- 5 S. Stefan, L. Andreas, Z. Veronika, R. Joseph, G. Steffen, R. Daniel and F. Jurgen,  $\text{Li}^+/\text{H}^+$  exchange of  $\text{Li}_7\text{La}_3\text{Zr}_2\text{O}_{12}$  single and polycrystals investigated by quantitative LIBS depth profiling, *Mater. Adv.*, 2022, **3**, 8760–8770.
- 6 J. X. Chen, P. Alessandro, Y. Shinhee, C. D. Valbjorn, E. Vincenzo and P. Nini, *Mater. Adv.*, 2023, **4**, 6638–6644.
- 7 X. M. Xia, S. T. Xu, F. Tang, Y. Yao, L. F. Wang, L. Liu, S. N. He, Y. X. Yang, W. P. Sun, C. Xu, Y. Z. Feng, H. G. Pan, X. H. Rui and Y. Yu, A multifunctional interphase layer enabling superior sodium-metal batteries under ambient temperature and  $-40\text{ }^{\circ}\text{C}$ , *Adv. Mater.*, 2023, **35**, 2209511.
- 8 J. J. Zhang and X. Wu, Dual-ion carrier storage through  $\text{Mg}^{2+}$  addition for high-energy and long-life zinc-ion hybrid capacitor, *Int. J. Miner., Metall. Mater.*, 2024, **31**, 179–185.
- 9 J. Xie and Q. C. Zhang, Recent progress in multivalent metal (Mg, Zn, Ca, and Al) and metal-ion rechargeable batteries with organic materials as promising electrodes, *Small*, 2019, **15**, 1805061.
- 10 X. Lv, F. Tang, Y. Yao, C. Xu, D. Chen, L. Liu, Y. Z. Feng, X. H. Rui and Y. Yu, Sodium gallium alloy layer for fast and reversible sodium deposition, *SusMat*, 2022, **2**, 699–707.
- 11 M. Zhao, S. L. Li and X. Wu,  $(\text{NH}_4)_2\text{V}_{10}\text{O}_{25.8}\text{H}_2\text{O}$  nanowire materials for stable zinc ion storage, *Mater. Today Chem.*, 2023, **33**, 101686.
- 12 Y. X. Zeng, X. Y. Zhang, R. F. Qin, X. Q. Liu, P. P. Fang, D. Z. Zheng, Y. X. Tong and X. H. Lu, Dendrite-free zinc deposition induced by multifunctional CNT frameworks for stable flexible Zn-ion batteries, *Adv. Mater.*, 2019, **31**, 1903675.
- 13 Y. Liu, Y. Liu, X. Wu and Y. R. Cho, General carbon modification avenue to construct highly stable  $\text{V}_2\text{O}_5$  electrodes for aqueous zinc-ion batteries, *ACS Sustainable Chem. Eng.*, 2023, **11**, 13298–13305.
- 14 S. Q. Zhao, Y. Liu and X. Wu, Rose-shaped  $\text{VS}_2$  nanosheets as cathode materials for rechargeable zinc ion batteries, *CrystEngComm*, 2023, **25**, 1986–1992.
- 15 Y. Liu and X. Wu, High durable aqueous zinc ion batteries by synergistic effect of  $\text{V}_6\text{O}_{13}/\text{VO}_2$  electrode materials, *J. Energy Chem.*, 2023, **87**, 334–341.
- 16 Y. X. Zeng, X. F. Lu, S. L. Zhang, D. Y. Luan, S. Li and X. W. Lou, Construction of Co-Mn prussian blue analog hollow spheres for efficient aqueous Zn-ion batteries, *Angew. Chem., Int. Ed.*, 2021, **60**, 22189–22194.
- 17 K. X. Li, Y. Liu and X. Wu,  $\text{Mn}^{2+}$  Intercalation into hydrated vanadium pentoxide nanosheets for highly durable zinc ion batteries, *ACS Appl. Nano Mater.*, 2023, **6**, 12439–12446.
- 18 F. X. Shi, C. C. Mang, H. W. Liu and Y. F. Dong, Flexible and high-energy-density Zn/ $\text{MnO}_2$  batteries enabled by electrochemically exfoliated graphene nanosheets, *New J. Chem.*, 2020, **44**, 653–657.
- 19 Y. Liu, Y. Liu, Y. Yamauchi, Z. A. Allothman, Y. V. Kaneti and X. Wu, Enhanced zinc ion storage capability of  $\text{V}_2\text{O}_5$  electrode materials with hollow interior cavities, *Batteries Supercaps*, 2021, **4**, 1867–1873.
- 20 Y. Liu and X. Wu, Hydrogen and sodium ions co-intercalated vanadium dioxide electrode materials with enhanced zinc ion storage capacity, *Nano Energy*, 2021, **86**, 106124.
- 21 F. Wan and Z. Q. Niu, Design strategies for vanadium-based aqueous zinc-ion batteries, *Angew. Chem., Int. Ed.*, 2019, **58**, 16358–16367.
- 22 X. Zhang, Y. C. Tang, P. He, Z. Zhang and T. F. Chen, Edgerich vertical graphene nanosheets templating  $\text{V}_2\text{O}_5$  for highly durable zinc ion battery, *Carbon*, 2021, **172**, 207–213.
- 23 X. Wang, Y. M. Wang, J. N. Hao, Y. Liu, H. H. Xiao, Y. Ma, L. M. Chen, Y. Y. Huang and G. H. Yuan, Pseudocapacitive zinc cation intercalation with superior kinetics enabled by atomically thin  $\text{V}_2\text{O}_5$  nanobelts for quasi-solid-state micro-batteries, *Energy Storage Mater.*, 2022, **50**, 454–463.
- 24 D. D. Zhang, J. Cao, Y. L. Yue, T. Pakornchote, T. Bovornratanaraks, J. Han, X. Y. Zhang, J. Q. Qin and Y. H. Huang, Two birds with one stone: boosting zinc-ion insertion/extraction kinetics and suppressing vanadium dissolution of  $\text{V}_2\text{O}_5$  via  $\text{La}^{3+}$  incorporation enable advanced zinc-ion batteries, *ACS Appl. Mater. Interface*, 2021, **13**, 38416–38424.
- 25 R. Li, F. Xing, T. Y. Li, H. M. Zhang, J. W. Yan, Q. Zheng and X. F. Li, Intercalated polyaniline in  $\text{V}_2\text{O}_5$  as a unique vanadium oxide bronze cathode for highly stable aqueous zinc ion battery, *Energy Storage Mater.*, 2021, **38**, 590–598.
- 26 Y. Liu, Y. Liu, X. Wu and Y. R. Cho, High performance aqueous zinc battery enabled by potassium ion stabilization, *J. Colloid Interface Sci.*, 2022, **628**, 33–40.
- 27 G. A. Sawatzky and D. Post, X-ray photoelectron and auger spectroscopy study of some vanadium oxides, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1979, **20**, 1546–1555.
- 28 F. Liu, Z. X. Chen, G. Z. Fang, Z. Q. Wang, Y. S. Cai, B. Y. Tang, J. Zhou and S. Q. Liang,  $\text{V}_2\text{O}_5$  nanospheres with mixed vanadium valences as high electrochemically active aqueous zinc-ion battery cathode, *Nano-Micro Lett.*, 2019, **11**, 25.
- 29 C. M. Ghimbeu, E. Raymundo-Pinero, P. Fioux, F. Beguin and C. Vix-Guterl, Vanadium nitride/carbon nanotube nanocomposites as electrodes for supercapacitors, *J. Mater. Chem. A*, 2011, **21**, 13268.
- 30 C. X. Liu, R. Li, W. J. Liu, G. Z. Shen and D. Chen, Chitosan-assisted fabrication of a network  $\text{C}@\text{V}_2\text{O}_5$  cathode for high-performance Zn-ion batteries, *ACS Appl. Mater. Interfaces*, 2021, **13**, 37194–37200.
- 31 Y. X. Zeng, Z. Z. Lai, Y. H. Han, H. Z. Zhang, S. L. Xie and X. H. Lu, Oxygen-vacancy and surface modulation of



- ultrathin nickel cobaltite nanosheets as a high-energy cathode for advanced Zn-ion batteries, *Adv. Mater.*, 2018, **33**, 1802396.
- 32 J. Zhang, C. Q. Dong, Z. B. Wang, H. Gao, J. Z. Niu, Z. Q. Peng and Z. H. Zhang, A new defect-rich CoGa layered double hydroxide as efficient and stable oxygen evolution electrocatalyst, *Small Methods*, 2019, **3**, 1800286.
- 33 Y. Liu, P. Hu, H. Liu, X. Wu and C. Zhi, Tetragonal VO<sub>2</sub> hollow nanospheres as robust cathode material for aqueous zinc ion batteries, *Mater. Today Energy*, 2020, **17**, 100431.
- 34 X. Y. Chen, L. B. Wang, H. Li, F. Y. Cheng and J. Chen, Porous V<sub>2</sub>O<sub>5</sub> nanofibers as cathode materials for rechargeable aqueous zinc-ion batteries, *J. Energy Chem.*, 2019, **38**, 20–25.
- 35 S. Y. Deng, H. Li, B. H. Chen, Z. J. Xu, Y. Jiang, C. H. Li, W. Xiao and X. M. Yan, High performance of Mn-doped VO<sub>2</sub> cathode for aqueous zinc-ion batteries: an insight into Zn<sup>2+</sup> storage mechanism, *Chem. Eng. J.*, 2023, **452**, 139115.
- 36 J. W. Li, K. McColl, X. K. Lu, S. Sathasivam, H. B. Dong, L. Q. Kang, Z. N. Li, S. Y. Zhao, A. G. Kafizas, R. Wang, D. J. L. Brett, P. R. Shearing, F. Cora, G. J. He, C. J. Carmalt and I. P. Parkin, Multi-Scale investigations of δ-Ni<sub>0.25</sub>V<sub>2</sub>O<sub>5</sub>·nH<sub>2</sub>O cathode materials in aqueous zinc-ion batteries, *Adv. Energy Mater.*, 2020, **10**, 2000058.
- 37 D. D. Jia, K. Zheng, M. Song, H. Tan, A. Zhang, L. H. Wang, L. J. Yue, D. Li, C. W. Li and J. Q. Liu, VO<sub>2</sub>·0.2H<sub>2</sub>O nanocuboids anchored onto graphene sheets as the cathode material for ultrahigh capacity aqueous zinc ion batteries, *Nano Res.*, 2020, **13**, 215–224.
- 38 W. J. Li, C. Han, Q. F. Gu, S. L. Chou, J. Z. Wang, H. K. Liu and S. X. Dou, Electron delocalization and dissolution-restraint in vanadium oxide superlattices to boost electrochemical performance of aqueous zinc-ion batteries, *Adv. Energy Mater.*, 2020, **10**, 2001852.
- 39 N. Qiu, Z. M. Yang, R. Xue, Y. Wang, Y. M. Zhu and W. Liu, Toward a high-performance aqueous zinc ion battery: potassium vanadate nanobelts and carbon enhanced zinc foil, *Nano Lett.*, 2021, **21**, 2738–2744.
- 40 X. Wang, B. J. Xi, X. J. Ma, Z. Y. Feng, Y. X. Jia, J. K. Feng, Y. T. Qian and S. L. Xiong, Boosting zinc-ion storage capability by effectively suppressing vanadium dissolution based on robust layered barium vanadate, *Nano Lett.*, 2020, **20**, 2899–2906.
- 41 H. G. Qin, L. L. Chen, L. M. Wang, X. Chen and Z. H. Yang, V<sub>2</sub>O<sub>5</sub> hollow spheres as high rate and long life cathode for aqueous rechargeable zinc ion batteries, *Electrochim. Acta*, 2019, **306**, 307–316.
- 42 H. F. Liang, Z. Cao, F. W. Ming, W. L. Zhang, D. H. Anjum, Y. Cui, L. Cavallo and H. N. Alshareef, Aqueous zinc-ion storage in MoS<sub>2</sub> by tuning the intercalation energy, *Nano Lett.*, 2019, **19**, 3199–3206.
- 43 Z. Y. Feng, Y. F. Zhang, J. J. Sun, Y. Y. Liu, H. M. Jiang, M. Cui, T. Hu and C. G. Meng, Dual ions enable vanadium oxide hydration with superior Zn<sup>2+</sup> storage for aqueous zinc-ion batteries, *Chem. Eng. J.*, 2022, **433**, 133795.

