


Cite this: *RSC Adv.*, 2024, 14, 20543

# La-doped MIL-88B(Fe)–NH<sub>2</sub>: a mixed-metal–organic framework photocatalyst for highly efficient reduction of Cr(vi) in an aqueous solution

Minh Hue Dang Thi,<sup>a</sup> Linh Giang Hoang Thi,<sup>a</sup> Chinh Dang Huynh,<sup>a</sup>  
Hoai Phuong Nguyen Thi <sup>b</sup> and Duc D. La <sup>\*cd</sup>

With the aim to resolve the problem of water pollution, we herein propose a new photocatalyst based on metal–organic frameworks (MOFs), called La-doped MIL-88B(Fe)–NH<sub>2</sub> (MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub>), which was designed and employed for the photocatalytic reduction of Cr(vi) in aqueous solutions. MIL-88B((1–x)Fe/xLa)–NH<sub>2</sub> materials with different *x* values were synthesized via a one-pot solvothermal method. Their characteristics were investigated using various techniques, including X-ray diffraction (XRD), scanning electron microscopy (SEM), energy-dispersive spectroscopy (EDS), Brunauer–Emmett–Teller (BET) analysis, Fourier-transform infrared (FT-IR) spectroscopy and ultraviolet-visible diffuse reflectance spectroscopy (UV-vis DRS). We found that compared to pristine MIL-88B(Fe)–NH<sub>2</sub> with a photocatalytic efficiency of 67.08, MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> materials with *x* = 0.010, 0.025 and 0.050 exhibit excellent photocatalytic efficiencies reaching 88.21, 81.19 and 80.26%, respectively, after only 30 minutes of irradiation at a small catalyst dosage of 0.2 g L<sup>–1</sup>. These La-doped MIL-88B(Fe)–NH<sub>2</sub> photocatalysts can work well under mild conditions (pH = 6). Furthermore, they are robust—can be recycled for at least four consecutive runs without any activity loss. This novel material is promising for the photocatalytic degradation of pollutants.

Received 7th May 2024  
Accepted 16th June 2024

DOI: 10.1039/d4ra03351e

rsc.li/rsc-advances

## Introduction

The increase in toxic heavy metal ion contamination in aquatic environments has become a serious issue worldwide. Hexavalent chromium (Cr(vi)) is a typical contaminant that is widely used in various industrial fields such as electroplating, leather tanning, cooling tower blowdown, and rinse waters.<sup>1</sup> Waste Cr(vi) compounds are discharged easily into water bodies and cause serious harm to human health and organisms.<sup>2</sup> Alternatively, Cr(III) is an essential trace metal involved in protein structure stabilization and glucose and lipid metabolism.<sup>3</sup> Therefore, reducing Cr(vi) to Cr(III) is considered an effective way for Cr(vi) removal from water.

A number of methods, including chemical, electrochemical and biological processes, are applied to aqueous Cr(vi) reduction.<sup>4</sup> Therein, the reduction of Cr(vi) to Cr(III) via a photocatalysis process is a fruitful method. This photocatalytic

technique is based on the electron/hole (e<sup>–</sup>/h<sup>+</sup>) pairs generated in semiconductor materials under light illumination whose photon energy is greater than the semiconductor's bandgap energy.<sup>5</sup> Many studies have reported the photocatalytic reduction of Cr(vi) over TiO<sub>2</sub>, which is the most widely studied photocatalyst.<sup>6–8</sup> However, its catalytic efficiency is limited by its large bandgap energy (3.2 eV) and the high recombination rate of photogenerated e<sup>–</sup>/h<sup>+</sup> pairs.<sup>9</sup>

Metal–organic frameworks (MOFs) are a class of porous and crystalline materials composed of metal ions/ion clusters and organic ligands. Large specific surface area, structural tunability and reversible adsorption are the outstanding features of MOFs.<sup>10</sup> As a result, MOFs can be applied to a series of applications such as catalysis,<sup>11,12</sup> gas storage and separation,<sup>13,14</sup> cell imaging,<sup>15</sup> and sensing.<sup>16</sup> In the catalysis area, in particular photocatalysis, MOFs have become dominant photocatalysts for treating water pollution because of their low e<sup>–</sup>/h<sup>+</sup> recombination probability due to ligand-to-metal charge transfer (LMCT).<sup>17,18</sup> Fe-based MOFs (Fe-MOFs) are a family of potential materials in this field owing to their relatively small bandgap in the range of 1.6–2.8 eV,<sup>11,12,19–22</sup> low toxicity and intrinsic stability.<sup>23</sup> Moreover, Fe-MOFs contain unsaturated iron(III) ions with high catalytic activity, and this ensures their catalytic ability in advanced oxidation processes (AOPs), in particular Fenton-like processes.<sup>23</sup> Among them, MIL-88B(Fe)–NH<sub>2</sub> (MIL: Materials of Institute Lavoisier) is a common Fe-MOF material

<sup>a</sup>School of Chemistry and Life Sciences, Hanoi University of Science and Technology, Hanoi, Vietnam

<sup>b</sup>Department of Chemistry and Environment, Joint Vietnam-Russia Tropical Science and Technology Research Center, 63 Nguyen Văn Huyen Street, Cau Giay, Ha Noi, Vietnam

<sup>c</sup>Laboratory of Advanced Materials Chemistry, Institute for Advanced Study in Technology, Ton Duc Thang University, Ho Chi Minh City, Vietnam. E-mail: laducduong@tdtu.edu.vn

<sup>d</sup>Faculty of Applied Sciences, Ton Duc Thang University, Ho Chi Minh City, Vietnam


whose structure is built up by trimers of iron(III) octahedra and 2-aminoterephthalate ligands.<sup>24</sup> Compared to other MOFs, MIL-88B(Fe)-NH<sub>2</sub> exhibits high catalytic ability,<sup>25</sup> chemical stability, structural flexibility, and abundant raw sources.<sup>16</sup> Hence, it attracts remarkable attention in a wide range of applications such as heterogeneous catalysis,<sup>26</sup> adsorption,<sup>27</sup> sensing<sup>16</sup> and batteries.<sup>28</sup>

Many strategies have been used in order to enhance the photocatalytic efficiency of MOFs as well as other semiconductors. In this aspect, mixing rare earth elements (REEs) (La, Ce, Sb and so on) with these materials has been proven to be a feasible solution.<sup>29–31</sup> Opposite to d-block metals, REE-metals have unique electronic properties because of their 4f electron configurations that are shielded from outermost sub-shell 5s and 5p, and REE-metals have distinct electronic and magnetic properties that are not significantly altered by coordinating ligands. Furthermore, REEs in general and lanthanum (<sup>57</sup>La) in particular are able to act as electron traps thanks to a plenty of empty orbitals in 4f and 5d subshells, thereby slowing down the e<sup>−</sup>/h<sup>+</sup> recombination rate and consequently improving the efficiency. The application of the Lanthanum-MOFs has been reported in various fields of catalysis, adsorption of toxic and heavy metal ions, and sensing. Further modification of La-Fe MOFs can improve the surface area and catalytic capability of the materials. In this work, we aimed to synthesize and apply La-doped MIL-88B(Fe)-NH<sub>2</sub> for the photocatalytic removal of Cr(VI). Various methods including X-ray diffraction (XRD), scanning electron microscopy (SEM), energy-dispersive spectroscopy (EDS), Brunauer–Emmett–Teller (BET) analysis, Fourier-transform infrared (FT-IR) spectroscopy, and ultraviolet-visible diffuse reflectance spectroscopy (UV-vis DRS) were employed to characterize the as-synthesized photocatalysts, and ultraviolet-visible (UV-vis) spectroscopy was used to determine the remaining Cr(VI) concentration in aqueous media. We found that the introduction of lanthanum(III) into the MIL-88B(Fe)-NH<sub>2</sub> structure enhances the efficiency of Cr(VI) removal. Besides, experiments with different lanthanum(III) contents were conducted to find out the influence of the mixed lanthanum(III) content on the efficiency of the Cr(VI) photoreduction.

## Results and discussion

### Characterizations of materials

Fig. 1 shows the XRD spectra of MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> ( $x = 0.010, 0.025, 0.050$  and  $0.10$ ) materials (abbreviated in the graph: MIL(FeLa)) under the solvothermal condition of 150 °C and 12 hours. As reported in our previous work on MIL-88B(Fe)-NH<sub>2</sub>,<sup>16</sup> two characteristic peaks of the MIL-88B(Fe)-NH<sub>2</sub> phase appeared at  $2\theta \approx 9.3$  and  $10.6^\circ$  corresponding to the (002) and (101) lattices (CCDC 647646). Two of these diffraction peaks also appear for the MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> materials, but they record a slight variation. In particular, the peak of the (002) lattice moves to a smaller angular position on the XRD pattern of all La<sup>3+</sup> ratios ( $2\theta \approx 9.2^\circ$ ). With the (101) lattice, the peak shifts to the position  $2\theta \approx 10.3^\circ$  in the samples with  $x = 0.010$  and  $0.025$ ,  $2\theta \approx 10.8^\circ$  in the sample with  $x = 0.050$ . More

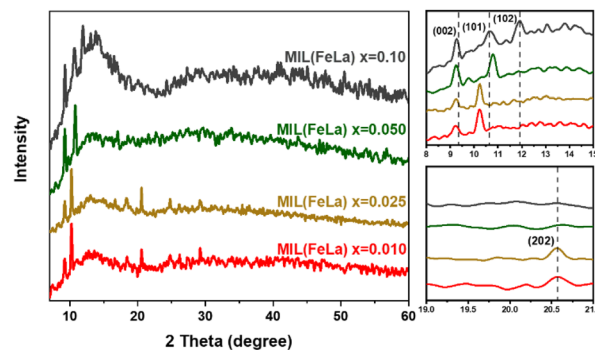


Fig. 1 XRD spectra of La-doped MIL-88B(Fe)-NH<sub>2</sub> materials (MIL(FeLa)) under the solvothermal condition: 150 °C and 12 hours.

characteristic peaks are observed at  $2\theta \approx 11.9^\circ$  (sample with  $x = 0.10$ ) and  $2\theta \approx 20.6^\circ$  (samples with  $x = 0.010$  and  $0.025$ ) corresponding to the (102) and (202) lattice surfaces of MIL-88B(Fe)-NH<sub>2</sub> (CCDC 647646). These shifts as well as the appearance of additional peaks on the XRD spectra of the La-doped MIL-88B(Fe)-NH<sub>2</sub> material are the result of the presence of La<sup>3+</sup> in the MIL-88B(Fe)-NH<sub>2</sub> structure.<sup>32</sup> Importantly, no impure phases exist in the MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> ( $x = 0.010, 0.025$  and  $0.050$ ) spectra, demonstrating the single-phase material. By contrast, the obtained MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> ( $x = 0.10$ ) material is impure, as proven by the appearance of strange peaks in the range  $2\theta \approx 12.5$ – $15.0^\circ$ . It could be the result of ligand competition between La<sup>3+</sup> and Fe<sup>3+</sup>, or/and the formation of other lanthanum compounds. The ligand competition between La<sup>3+</sup> and Fe<sup>3+</sup> could lead to the formation of separate La-based MOFs. Many previous studies about MOF materials based on rare earth elements revealed that their MOF structure is complex and consequently difficult to determine because they are mostly built by metal ion chains with a large coordination number (usually 9).<sup>33</sup> Besides, some La(III) compounds could form during the reaction such as La(NO<sub>3</sub>)<sub>3</sub>,<sup>34</sup> LaCl<sub>3</sub>,<sup>35</sup> LaClO and La(OH)<sub>3</sub>.<sup>36</sup> These findings revealed that MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> was successfully synthesized at  $x$  values equal to 0.010, 0.025 and 0.050.

Morphology and particle size distribution of MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> ( $x = 0.010, 0.025$  and  $0.050$ ) materials are presented in Fig. 2. The material particles show a bipyramidal hexagonal prism shape, similar to previous works on MIL-88B(Fe)-NH<sub>2</sub>.<sup>16,19,37–39</sup> Furthermore, a relatively uniform distribution of the particles in all materials is observed. The size distribution and mean size were calculated using the ImageJ software, and the outcomes record changes in the particle size in the obtained MOFs. The average widths of MIL-88B((1 − x)Fe/xLa)-NH<sub>2</sub> at  $x = 0.010, 0.025$  and  $0.050$  are 462.5, 529.5 and 842.5 nm, respectively; corresponding to the average length/width ratio of 3.42; 2.76 and 2.11 (Table 1). It can be seen that the width size is proportional to the La<sup>3+</sup> content, whereas the trend of the length/width ratio is opposite. The large radius of the La<sup>3+</sup> ion compared to Fe<sup>3+</sup> and the structural swell may cause this change.<sup>32</sup>



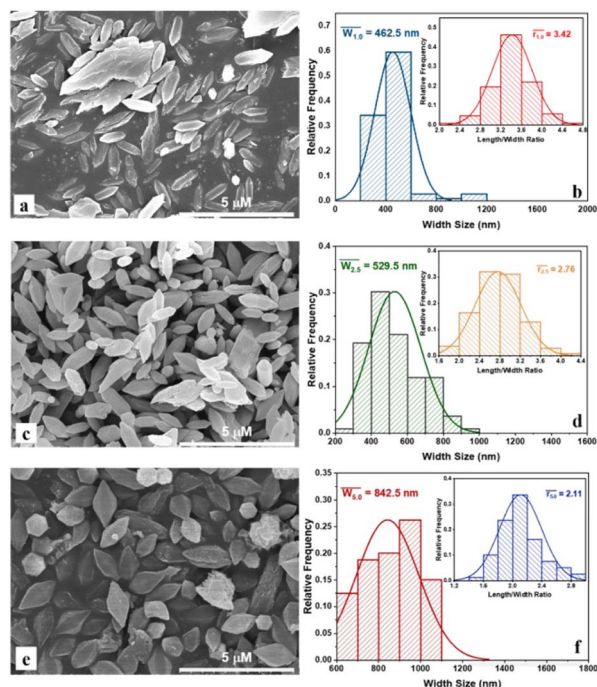


Fig. 2 SEM images and particle size distribution of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> with x = 0.010 (a and b), x = 0.025 (c and d) and x = 0.050 (e and f).

The EDS analysis technique was employed to determine the element compositions of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010), as shown in Fig. 3. The results indicate the presence of La elements in the MIL-88B(Fe)-NH<sub>2</sub> structure.

The N<sub>2</sub> adsorption-desorption isotherm analysis (BET) of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) is shown in Fig. 4. It can be seen that the N<sub>2</sub> adsorption-desorption curve of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) displayed type IV isotherms with hysteresis corresponding to capillary condensation, which is typical of mesoporous materials. The measured surface area from BET analysis (*S*<sub>BET</sub>) of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) is 35.3 m<sup>2</sup> g<sup>-1</sup> (Fig. 4). Normally, the *S*<sub>BET</sub> values of Fe-MOF materials are lower than those of other MOF families<sup>40,41</sup> due to their closed micropore structure (Table 2). Micropores in the Fe-MOFs' structure are incompatible with N<sub>2</sub> in terms of size, thereby restricting N<sub>2</sub> adsorption.<sup>45,46</sup> Besides, the surface area of Fe-MOFs is affected by different synthesis conditions and methods as well.

Fig. 5 shows infrared spectra of the NH<sub>2</sub>-TPA ligand, MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) materials. Two peaks at 3462 and 3334 cm<sup>-1</sup> are attributed to the asymmetric and symmetric stretching vibrations of N-H

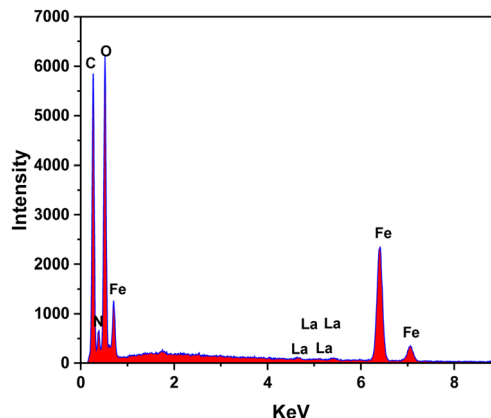


Fig. 3 EDS spectrum of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010).

bonds, respectively. Similarly, two peaks appear at 1567 and 1367 cm<sup>-1</sup> due to the asymmetric and symmetric C-O stretching oscillation. A peak at 1682 cm<sup>-1</sup> represents the presence of the C=O group. The peaks at 1252 cm<sup>-1</sup> and 766 cm<sup>-1</sup> correspond to C<sub>sp</sub><sup>2</sup>-N and C<sub>sp</sub><sup>2</sup>-H bending vibrations. All of these summits are observed in the infrared graph of the TPA-NH<sub>2</sub> ligand and the as-synthesized MOFs. Additionally, in the spectrum of MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010), there appear other peaks which characterize new binding vibrations. Particularly, the peak appears at 3327 cm<sup>-1</sup> due to the presence of O-H vibration that belongs to H<sub>2</sub>O molecules adsorbed in the MOF material. The characteristic vibrations of Fe-O and La-O bonds are observed at 507 cm<sup>-1</sup>, evidence of the binding formation among Fe<sup>3+</sup>, La<sup>3+</sup> and the COO- groups in the ligand. As such, the FT-IR results contribute to confirming the bond formation of the metal centers with the ligand as well as the structural stability when induced by the La<sup>3+</sup> ion.

Fig. 6a shows the UV-vis DRS results of MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010, 0.025 and 0.050) materials. Compared to the original MIL-88B(Fe)-NH<sub>2</sub> material, the wavelength at which the maximum absorption of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> materials takes place does not change significantly, but there is difference in absorption intensity. MIL-88B(Fe)-NH<sub>2</sub> has the maximum wavelength (λ<sub>max</sub>) at 390 nm with an absorption edge extending to the visible light region while the absorbance in the spectra of the MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010, 0.025 and 0.050) drops slightly.

The bandgap energies of MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010, 0.025 and 0.050) photocatalysts were determined using the Kubelka-Munk equation and the Tauc plot<sup>47</sup> as follows:

Table 1 Average particle sizes of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> materials

Average values	MIL-88B((1 - x)Fe/xLa)-NH <sub>2</sub> (x = 0.010)	MIL-88B((1 - x)Fe/xLa)-NH <sub>2</sub> (x = 0.025)	MIL-88B((1 - x)Fe/xLa)-NH <sub>2</sub> (x = 0.050)
Width (nm)	462.5	529.5	842.5
Length/width ratio	3.42	2.76	2.11

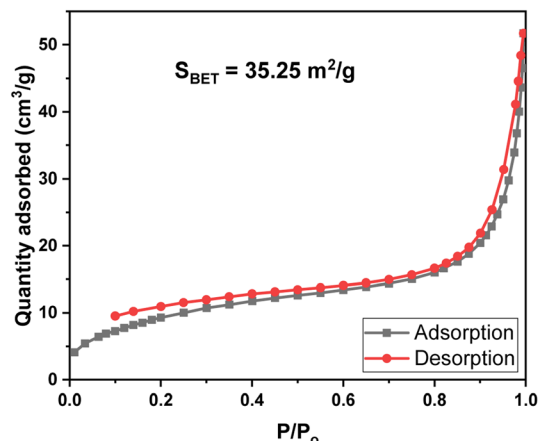


Fig. 4 N<sub>2</sub> adsorption-desorption isotherms of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010).

$$(\alpha h\nu)^2 = A(h\nu - E_g)$$

where  $\alpha$  is the absorption coefficient,  $h$  is Planck's constant,  $\nu$  is the photon's frequency,  $A$  is a proportionality constant and  $E_g$  is the bandgap energy.

As shown in Fig. 6b, the bandgap energy ( $E_g$ ) increases from 1.99, 2.00, 2.23 and 2.41 eV corresponding to the  $x$  value increasing from 0 (MIL-88B(Fe)-NH<sub>2</sub>) to 0.050. It can be seen that La<sup>3+</sup> inserted into the MIL-88B(Fe)-NH<sub>2</sub> structure expands the bandgap energy, and this energy increases proportionally to the La<sup>3+</sup> content. This widening can be explained by the Burstein-Moss effect.<sup>48</sup> La<sup>3+</sup> tends to contribute more electrons than Fe<sup>3+</sup> because the large ionic radius of La<sup>3+</sup> reduces the electrostatic interaction between the outer electrons and the nucleus, leading to the Fermi level being filled with electrons. Therefore, the following excited electrons can only move to an energy state higher than the Fermi level, causing the bandgap expansion. Moreover, crystal defects can be a factor that makes the  $E_g$  value shift, and a decrease in crystal defects results in the  $E_g$  increase.<sup>49</sup> The binding energy of La-O is stronger than that of Fe-O ( $E_{\text{La-O}} = 798 \text{ kJ mol}^{-1} > E_{\text{Fe-O}} = 407 \text{ kJ mol}^{-1}$  (ref. 50)) which contributes to reducing the number of defects in the crystal lattice.

### Photocatalytic study

The results of UV-vis spectra of the Cr-DPC complex solution at various reaction intervals in the range of 2–14 minutes and its

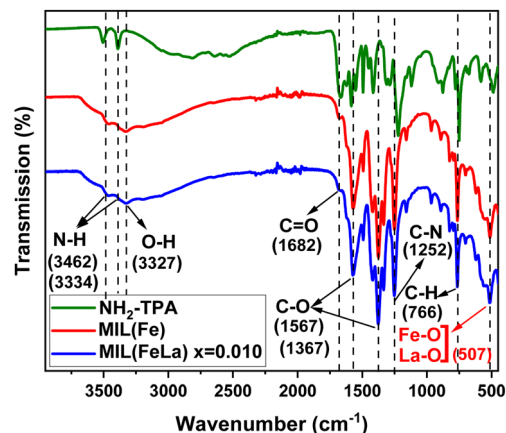


Fig. 5 FT-IR spectra of NH<sub>2</sub>-TPA, MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010).

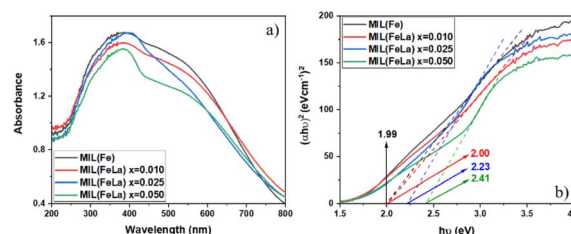


Fig. 6 UV-vis-DRS spectra (a) and Tauc plots (b) of MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010, 0.025 and 0.050).

time-absorbance line graph are indicated in Fig. 7a and b. The output reveals that the maximum absorbance reaches a wavelength of 550 nm ( $\lambda_{\text{max}} = 550 \text{ nm}$ ),<sup>51</sup> and the absorbance of the Cr-DPC solution remains stable after 11 minutes. Therefore, the absorbance of the following Cr-DPC solutions is measured at  $\lambda_{\text{max}} = 550 \text{ nm}$  after 11 minutes of reaction. To determine the linear range between the Cr(vi) concentration and the absorbance, we built two calibration curves in the Cr(vi) concentration range of 1–25 ppm (Fig. 7c and d). Linearity is observed from 1 ppm to 20 ppm using equation  $A = 0.0196[\text{Cr(vi)}] + 0.0030$  ( $R^2 = 0.9988$ ).

Previous studies have reported that the pH environment has considerable effects on the Cr(vi) photoreduction ability.<sup>11,52,53</sup> Under a basic condition, the existing form of Cr(OH)<sub>3</sub> precipitation of Cr(III) can cover active sites on the catalyst surface

Table 2 Comparison of the BET surface area of MIL-88B((1 - x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) with other Fe-MOFs

Material	Synthesis method (solvent)	$S_{\text{BET}}$ (m <sup>2</sup> g <sup>-1</sup> )	References
MIL-53(Fe)	Solvothermal	6.48	42
MIL-53(Fe)	Solvothermal	9.77	43
MIL-88B(Fe)-NH <sub>2</sub>	Solvothermal	19.2	44
MIL-88B(Fe)-NH <sub>2</sub>	Solvothermal (H <sub>2</sub> O/ethanol)	2.35	43
MIL-88B(Fe)-NH <sub>2</sub>	Solvothermal (DMF/ethanol)	8.9	42
MIL-88B(Fe)-NH <sub>2</sub>	Solvothermal (DMF)	13.43	16
MIL-88B((1 - x)Fe/xLa)-NH <sub>2</sub> (x = 0.010)	Solvothermal (DMF)	35.25	This work





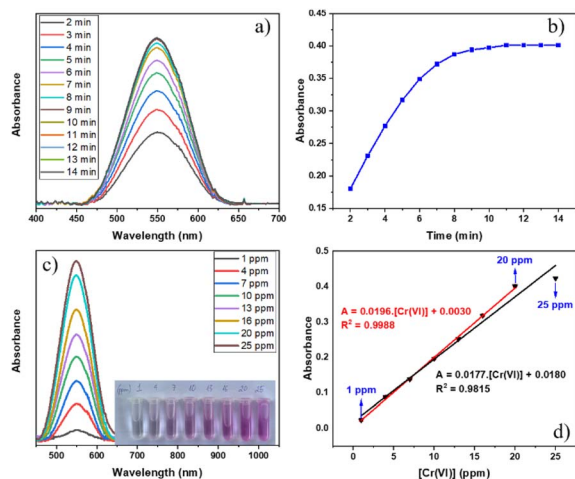


Fig. 7 (a) Adsorption spectra and (b) time-absorbance line graph of the Cr–DPC complex. (c) Adsorption spectra of Cr–DPC complex solutions with different initial Cr(vi) concentrations and (d) linear relationship between the absorbance at 550 nm and Cr(vi) concentration.

leading to a reduction in the efficiency. Therefore, our work focused on evaluating the pH influence on the catalytic activity for the photoreduction of Cr(vi) to Cr(III) using the MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) material under acidic, neutral and weak alkaline conditions, pH = 2–8 (Fig. 8). It can be seen that the weak acid environment is suitable for Cr(vi) reduction, and the best efficiency reaches 88.21% at pH = 6. The efficiency drops significantly when the pH increases, remaining at about 53% at pH = 7 and 43% at pH = 8. The same trend is observed when the pH value is below 6: the lower the pH, the poorer the performance.

Different existing species of Cr(vi) and Cr(III) may affect the material's catalytic efficiency. In the pH range from 2 to 6, Cr(vi) exists in Cr<sub>2</sub>O<sub>7</sub><sup>2–</sup> and HCrO<sub>4</sub><sup>–</sup> forms, and Cr(III) exists in [Cr(H<sub>2</sub>O)<sub>6</sub>]<sup>3+</sup>, Cr(OH)<sub>2</sub><sup>+</sup>, Cr(OH)<sub>2</sub><sup>2+</sup> and Cr(OH)<sub>3</sub> colloid forms.<sup>54</sup> Meanwhile, in the neutral and weak alkaline environment (6 < pH < 8), CrO<sub>4</sub><sup>2–</sup> and Cr(OH)<sub>3</sub> solids are the main forms of Cr(vi) and Cr(III), respectively.<sup>54</sup> Under neutral and weak alkaline conditions, the CrO<sub>4</sub><sup>2–</sup> form of Cr(vi) can inhibit the reduction process due to the low redox potential of CrO<sub>4</sub><sup>2–</sup>/Cr(OH)<sub>3</sub> (*E*<sup>0</sup>

–0.13 V).<sup>55</sup> Besides, the Cr(OH)<sub>3</sub> solid can mask active sites, leading to the limitation of the material's catalytic activity. In the acidic environment, the lower the pH, the higher the redox potential of Cr(vi)/Cr(III) (*E*<sub>Cr(vi)/Cr(III)</sub>), which is beneficial for the reduction of Cr(vi) to Cr(III). Nonetheless, the results show the achieved highest performance at pH = 6. Thus, the Cr(vi) conversion performance can be affected by a Fenton-like process. Fe<sup>3+</sup> ions in the structure can react with H<sub>2</sub>O<sub>2</sub>, which increases the number of Fe<sup>2+</sup> ions *via* the Fenton mechanism (Fe<sup>3+</sup> + H<sub>2</sub>O<sub>2</sub> ↔ Fe<sup>2+</sup> + H<sup>+</sup> + HO<sub>2</sub><sup>•</sup>)<sup>56</sup> – a reducing agent can participate directly in the Cr(vi) reduction (*E*<sup>0</sup>(Fe<sup>3+</sup>/Fe<sup>2+</sup>) = 0.771 eV, *E*<sup>0</sup>(HCrO<sub>4</sub><sup>–</sup>/Cr<sup>3+</sup>) = 1.350 eV, *E*<sup>0</sup>(Cr<sub>2</sub>O<sub>7</sub><sup>2–</sup>/Cr<sup>3+</sup>) = 1.36 eV<sup>57</sup>).

Briefly, pH 6 was determined to be the optimal condition of MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) for the photoreduction of Cr(vi) to Cr(III). Subsequent experiments including assessing the photocatalytic ability of MIL-88B(Fe)-NH<sub>2</sub> and La-doped MIL-88B(Fe)-NH<sub>2</sub> photocatalysts and studying the photocatalytic kinetics and reusability of the catalyst would be conducted at this pH level.

The photocatalytic activity of MIL-88B(Fe)-NH<sub>2</sub> and MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> (x = 0.010, 0.025, and 0.050) was evaluated by the degradation of 20 ppm Cr(vi) (pH = 6) with a catalyst dosage of 0.2 g L<sup>–1</sup> in the presence of 3% H<sub>2</sub>O<sub>2</sub> (1 mL L<sup>–1</sup>) under UV irradiation. Control tests were also performed using: (i) only Cr(vi) solution (without catalysts and H<sub>2</sub>O<sub>2</sub>), and (ii) Cr(vi) solution with only H<sub>2</sub>O<sub>2</sub>. As shown in Fig. 9a, there is no change in Cr(vi) concentration in the control test (i) and the Cr(vi) concentration change in the test (ii) was relatively low (approximately 25.2% after 30 minutes of UV irradiation). Meanwhile, the Cr(vi) reduction of MIL-88B-NH<sub>2</sub> photocatalysts occurs rapidly, especially in first 2 minutes. The La-doped MIL-88B(Fe)-NH<sub>2</sub> materials exhibit a better catalytic ability, with efficiencies reaching 88.21, 81.19 and 80.26% for MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> with x = 0.010, 0.025 and 0.050, respectively, than that of MIL-88B(Fe)-NH<sub>2</sub>, with an efficiency of 67.08, after 30 minutes of irradiation. Obviously, the performance is improved when using La-doped MIL-88B(Fe)-NH<sub>2</sub> catalysts. Introducing a small amount of La<sup>3+</sup> into various nanomaterials such as MOFs, COFs, perovskites and semiconductor materials has been demonstrated to slow down the e<sup>–</sup>/h<sup>+</sup> recombination

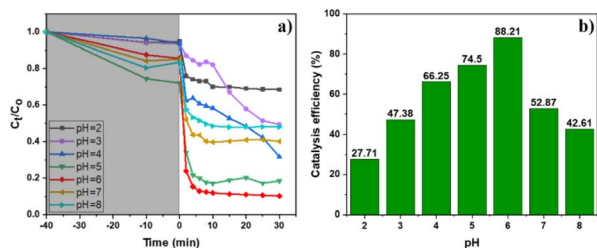


Fig. 8 Effect of pH on the photocatalytic performance of MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> (x = 0.010) (initial Cr(vi) concentration: 20 ppm; catalyst dosage: 0.2 g L; H<sub>2</sub>O<sub>2</sub>: 3% (1 mL L<sup>–1</sup>); UV irradiation): (a) Cr(vi) removal efficiency at different time and pH solution and (b) Cr(vi) removal efficiencies at different pH solutions.

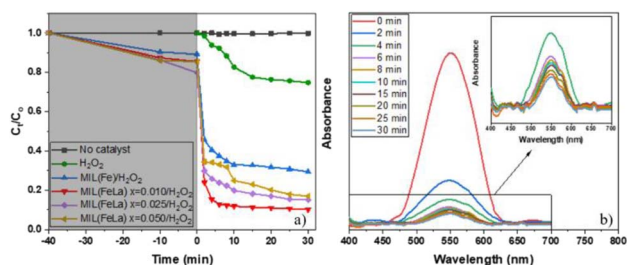


Fig. 9 Cr(vi) photoreduction of various materials over time (a) and absorbance spectra of Cr–DPC solutions after photoreduction over MIL-88B((1 – x)Fe/xLa)-NH<sub>2</sub> x = 0.010 (b) (initial Cr(vi) concentration: 20 ppm; pH = 6; catalyst dosage: 0.2 g L; H<sub>2</sub>O<sub>2</sub>: 3% (1 mL L<sup>–1</sup>); UV irradiation).



rate, thereby enhancing the catalytic activity.<sup>30,58,59</sup> As such, the  $\text{La}^{3+}$  appearance in the MIL-88B- $\text{NH}_2$  structure could inhibit the  $\text{e}^-/\text{h}^+$  recombination process, and the  $\text{Cr}(\text{vi})$  photocatalytic efficiency here could be decided by the  $\text{e}^-/\text{h}^+$  recombination rate.

Moreover, the highest amount of  $\text{Cr}(\text{vi})$  is reduced when using MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  with  $x = 0.010$  (88.21%), and a slight decreasing trend is recorded when the  $\text{La}^{3+}$  content increases, 81.19% for MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.025$ ) and 80.26% for MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.050$ ). In comparison with the  $E_g$  values of MIL-88B(Fe/La)- $\text{NH}_2$  materials (2.00 eV at  $x = 0.010$ ; 2.23 eV at  $x = 0.025$ ; and 2.41 eV at  $x = 0.050$ ), the catalytic performance of the material with a higher bandgap energy is lower. Therefore, the performance is impacted partially by the increase in the bandgap energy.

From the above-mentioned findings, MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) is selected to continue further research on the photoreduction process of  $\text{Cr}(\text{vi})$  to  $\text{Cr}(\text{iii})$  in water.

To evaluate the influence of  $\text{H}_2\text{O}_2$  on the photocatalytic performance, another control experiment was performed:  $\text{Cr}(\text{vi})$  degradation using photocatalyst MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) without  $\text{H}_2\text{O}_2$  (pH = 6). The obtained efficiency is only about 35%, considerably lower than that achieved when using the photocatalyst in the presence of  $\text{H}_2\text{O}_2$  (Fig. 10). Apparently,  $\text{H}_2\text{O}_2$  plays an important role in the photoreduction process of  $\text{Cr}(\text{vi})$  to  $\text{Cr}(\text{iii})$ . It helps  $\text{e}^-/\text{h}^+$  separation to be more fruitful thanks to combining with  $\text{e}^-$  ( $\text{e}^- + \text{H}_2\text{O}_2 \rightarrow \cdot\text{OH} + \text{OH}^-$ ),<sup>20</sup> thereby limiting the ability to recombine  $\text{e}^-/\text{h}^+$  and promoting the conversion process. In addition, the conversion performance is also enhanced by the production of reducing agent  $\text{Fe}^{2+}$  via the reaction of  $\text{Fe}^{3+}$  and  $\text{H}_2\text{O}_2$ :  $\text{Fe}^{3+} + \text{H}_2\text{O}_2 \leftrightarrow \text{Fe}^{2+} + \text{H}^+ + \text{HO}_2^\cdot$ .<sup>56</sup>

In terms of kinetics, pseudo-first-order (1.1) and pseudo-second-order (1.2) kinetic models were used to study the kinetics of the photocatalytic reaction of  $\text{Cr}(\text{vi})$  reduction on MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) for first five minutes. The calculated results show that the photocatalytic reaction obeys the pseudo-first-order model with a rate constant  $k_1 = 0.308 \text{ min}^{-1}$  ( $R^2 = 0.9925$ ) (Fig. 11). The MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) material exhibits a significantly higher rate

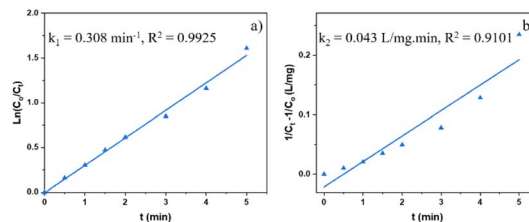


Fig. 11 Pseudo-1st- (a) and pseudo-2nd-order (b) kinetic models for the photocatalysis process of MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) (dosage:  $0.2 \text{ g L}^{-1}$ ).

constant than that of some other MOFs such as  $\text{NH}_2$ -ZIF-8 ( $0.0057 \text{ min}^{-1}$ ),<sup>60</sup>  $\text{NH}_2$ -MIL-88B(Fe)/CD-50 ( $0.0220 \text{ min}^{-1}$ ),<sup>19</sup> NNU-36 ( $0.0468 \text{ min}^{-1}$ )<sup>61</sup> and MIL-53(Fe) ( $0.1154 \text{ min}^{-1}$ ),<sup>52</sup> suggesting its high efficiency.

$$\ln(C_0/C_t) = k_1 t \quad (1.1)$$

$$\frac{1}{C_t} - \frac{1}{C_0} = k_2 t \quad (1.2)$$

where  $t$  is the reaction time (min);  $C_0$  and  $C$  correspond to initial and remaining concentrations of  $\text{Cr}(\text{vi})$  ( $\text{mg L}^{-1}$ );  $k_1$  ( $\text{min}^{-1}$ ) and  $k_2$  ( $\text{L mg}^{-1} \text{ min}^{-1}$ ) correspond to rate constants of the pseudo-1st- and 2nd-order models.

The stability of the MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) photocatalyst was tested by recovering and reusing 4 times. Obviously, the photodegradation of  $\text{Cr}(\text{vi})$  remains relatively stable in the subsequent runs, as shown in Fig. 12, indicating the high stability of the material. It can be seen that MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) shows good photocatalytic ability with high performance and high stability in comparison to previous works.<sup>19,53,60</sup>

MIL-88B(Fe)- $\text{NH}_2$  was reported to be an effective photocatalyst in the reduction of aqueous  $\text{Cr}(\text{vi})$  thanks to the LMCT mechanism.<sup>62,63</sup> Based on this, the proposed mechanism of MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) for the photoreduction of  $\text{Cr}(\text{vi})$  to  $\text{Cr}(\text{iii})$  in water is described as follows (Fig. 13): under

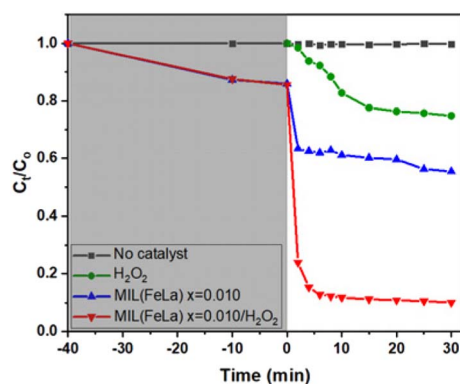


Fig. 10  $\text{Cr}(\text{vi})$  photoreduction over time of  $\text{H}_2\text{O}_2$ , MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ) (without/with  $\text{H}_2\text{O}_2$ ).

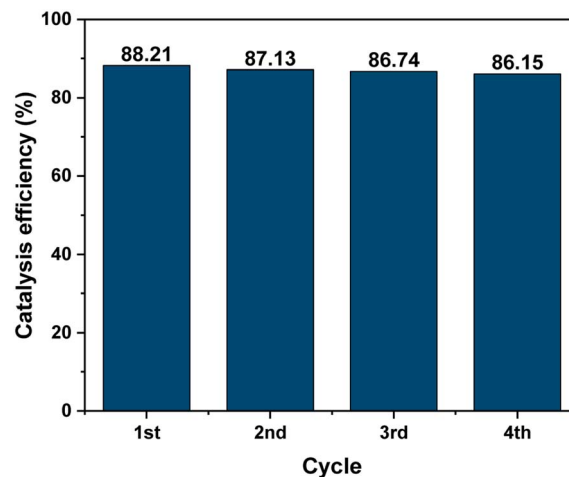


Fig. 12 Reusability of MIL-88B((1 -  $x$ )/Fe/ $x$ La)- $\text{NH}_2$  ( $x = 0.010$ ).











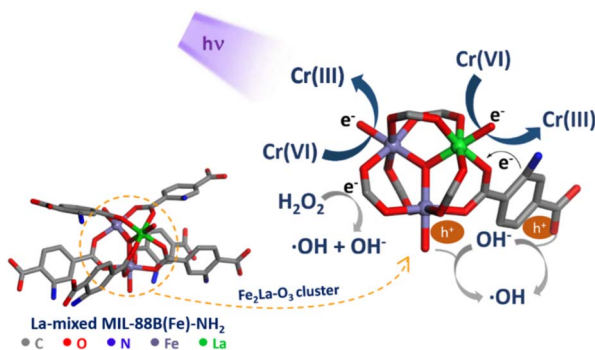


Fig. 13 Proposed mechanism of Cr(vi) photoreduction onto La-doped MIL-88B(Fe)-NH<sub>2</sub>.

UV irradiation, both the NH<sub>2</sub>-TPA ligand and the Fe<sub>3-n</sub>La<sub>n</sub>O cluster ( $n = 0, 1, 2$ , and  $3$ ) are excited. Fe<sub>3-n</sub>La<sub>n</sub>O clusters generate  $e^-/h^+$  pairs by absorbing photon energy, and electrons move to the conduction band leaving holes in the valence band (reaction (1)). The photoexcited electrons in the ligand move to the ion metal cluster, and this path is promoted more by amino groups. These generated electrons mainly participate in the reduction of Cr(vi) to Cr(III) (reaction (2)). The probability of  $e^-/h^+$  recombination is minimized thanks to the  $e^-$  trapping ability of H<sub>2</sub>O<sub>2</sub> (reaction (3)), and the  $h^+$  trapping ability of OH<sup>-</sup> ions (generated from reaction (3)<sup>64</sup>) and H<sub>2</sub>O molecules (reactions (4) and (5)). Furthermore, Fe<sup>2+</sup> ions produced from the Fenton reaction and  $\cdot O_2^-$  radicals produced from oxygen reduction by photoelectrons also contribute to Cr(vi) reduction (reactions (6–10)).



## Experimental

### Chemicals and instrumentation

Iron(III) chloride hexahydrate (FeCl<sub>3</sub>·6H<sub>2</sub>O; 99% wt), lanthanum(III) nitrate hexahydrate (La(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O; 98% wt), 2-amino-terephthalic acid (H<sub>2</sub>N-C<sub>6</sub>H<sub>3</sub>-1,4-(COOH)<sub>2</sub> (NH<sub>2</sub>-TPA); 99% wt),

methanol (CH<sub>3</sub>OH (MeOH); 99.8% v/v), ethanol (C<sub>2</sub>H<sub>5</sub>OH (EtOH); 99.5% v/v), potassium dichromate (K<sub>2</sub>Cr<sub>2</sub>O<sub>7</sub>; 99.8% wt), 1,5-diphenylcarbazide ((C<sub>6</sub>H<sub>5</sub>NHNH)<sub>2</sub>CO (DPC); 98% wt), sodium hydroxide (NaOH; 97% wt) and hydrochloric acid (HCl; 37% wt) were purchased from Sigma-Aldrich. Dimethylformamide (C<sub>3</sub>H<sub>7</sub>NO (DMF); 99.94% v/v) was purchased from Fisher Chemical.

A Siemens D5005 diffractometer (Cu-K<sub>α</sub> radiation,  $\lambda = 1.54056 \text{ \AA}$ ), a Hitachi S4800 scanning electron microscope, an ISIS 300 energy-dispersive X-ray spectrometer, a Gemini VII 2390 surface analyzer, a NICOLET iS50FT-IR spectrometer and a V-750 UV-visible spectrophotometer were used to perform XRD, SEM, EDS, BET, FT-IR and UV-vis DRS measurements, respectively. An Agilent 8453 UV-visible spectroscopy system was used to support for the determination of Cr(vi) concentrations.

### Synthesis of La-doped MIL-88B(Fe)-NH<sub>2</sub>

The fabrication process of La-doped MIL-88B(Fe)-NH<sub>2</sub> was referred from that of MIL-88B(Fe)-NH<sub>2</sub>, as reported in our previous work.<sup>16</sup> In particular, MIL-88B((1 -  $x$ )Fe/ $x$ La)-NH<sub>2</sub> materials were synthesized by an one-pot solvothermal method using a DMF solvent with a fixed molar ratio of H<sub>2</sub>N-C<sub>6</sub>H<sub>3</sub>-1,4-(COOH)<sub>2</sub> (NH<sub>2</sub>-TPA) ligand to metal ions of 1.5, under reaction conditions of 150 °C and 12 hours ( $x$ : the molar ratio of La<sup>3+</sup> to the molar total of the metal ion,  $x = \frac{n_{\text{La}^{3+}}}{n_{\text{La}^{3+}} + n_{\text{Fe}^{3+}}}$ ). An appropriate amount of FeCl<sub>3</sub>·6H<sub>2</sub>O and La(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O, and 0.6268 g NH<sub>2</sub>-TPA were dissolved into 50 mL DMF so that  $x$  reaches values of 0.010, 0.025, 0.050 and 0.10. The obtained solutions were sealed in autoclaves and then heated at 150 °C within 12 hours. Afterward, solid products were washed with DMF, methanol and distilled water and subsequently dried in a vacuum dryer. The fabricated MIL-88B((1 -  $x$ )Fe/ $x$ La)-NH<sub>2</sub> materials are in a brown-colored powder form.

### Photocatalytic experiments

The photocatalytic performance of La-doped MIL-88B(Fe)-NH<sub>2</sub> materials was studied through the photocatalytic reduction of Cr(vi) using a Hg lamp (250 W) as an ultraviolet light source.

The photoreduction efficiency of MIL-88B((1 -  $x$ )Fe/ $x$ La)-NH<sub>2</sub> ( $x = 0.010$ ) towards aqueous Cr(vi) solutions with different pH values was evaluated to study the influence of pH environment on the material's photocatalysis activity. The investigated pH values were in the range of 2–8, adjusted by HCl and NaOH. Particularly, the photocatalyst was dispersed in the Cr(vi)-containing solution (initial Cr(vi) concentration: 20 ppm; photocatalyst dosage: 0.2 g L<sup>-1</sup>) in a glass beaker in the darkness until an adsorption-desorption equilibrium was reached. Next, 3% H<sub>2</sub>O<sub>2</sub> solution was added into the reaction system (1 mL L<sup>-1</sup>), and illuminated at the same time. Subsequently, the mixture was collected at determined intervals, and the catalyst was separated by centrifugation. The Cr(vi) concentration was then determined by a diphenylcarbazide method. In this method, Cr(vi) ions react with 1,5-diphenylcarbazide (DPC) ligands to

form a purple-coloured complex (Cr–DPC complex) under the acidic condition.<sup>51,65</sup>

After finding out the optimal pH condition, similar experiments were performed to assess the Cr(VI) photoreduction ability of MIL-88B(Fe)–NH<sub>2</sub> and MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> (x = 0.010, 0.025, and 0.050) materials, impacts of H<sub>2</sub>O<sub>2</sub> appearance on the Cr(VI) photoreduction, photocatalytic kinetics and reusability of the photocatalyst.

## Conclusions

In summary, a series of MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> materials have been synthesized *via* a one-pot solvothermal approach and characterized by various measurement techniques including XRD, SEM, SEM-EDS, BET analysis, FT-IR spectroscopy and UV-vis DRS. The results indicate that MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> materials were fabricated successfully at x = 0.010, 0.025 and 0.050. MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> (x = 0.010, 0.025 and 0.050) materials were then used as photocatalysts for the aqueous Cr(VI) reduction. Compared to pristine MIL-88B(Fe)–NH<sub>2</sub>, La-doped MIL-88B(Fe)–NH<sub>2</sub> materials display a better photocatalytic efficiency, and the best is achieved on MIL-88B((1 – x)Fe/xLa)–NH<sub>2</sub> (x = 0.010). In addition, the impact of the pH environment on the reduction performance of Cr(VI), the photocatalytic kinetics and reusability of this catalyst were studied. The output shows that the kinetics of photocatalytic reaction follows the pseudo-1st-order model, and the material exhibits high efficiency under the weak acidic condition and high stability after 4 running cycles. The harvested knowledge in this work is expected to contribute to the development of mixed-MOFs in the catalysis area for wastewater treatment.

## Data availability

Data for this article, including SEM, EDX, XRD, BET surface area, FTIR, and photocatalytic results are available at Open Science Framework at <https://osf.io/me67s>.

## Author contributions

MHDT, LGDT: investigation, data collection, writing – original draft preparation. HPNT: resources, reviewing and editing; DCH, DDL: writing – reviewing and editing. DDL, MHDT: visualization, editing, funding acquisition & supervision. All authors approved the manuscript.

## Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## Acknowledgements

This work thanks to School of Chemistry and Life Sciences for the facility support.

## Notes and references

- 1 D. Mohan and C. U. Pittman Jr, Activated carbons and low cost adsorbents for remediation of tri- and hexavalent chromium from water, *J. Hazard. Mater.*, 2006, **137**(2), 762–811.
- 2 Z. Rahman and V. P. Singh, The relative impact of toxic heavy metals (THMs)(arsenic (As), cadmium (Cd), chromium (Cr)(VI), mercury (Hg), and lead (Pb)) on the total environment: an overview, *Environ. Monit. Assess.*, 2019, **191**, 1–21.
- 3 H. Ksheminska, D. Fedorovych, L. Babyak, D. Yanovych, P. Kaszycki and H. Koloczec, Chromium (III) and (VI) tolerance and bioaccumulation in yeast: a survey of cellular chromium content in selected strains of representative genera, *Process Biochem.*, 2005, **40**(5), 1565–1572.
- 4 C. E. Barrera-Díaz, V. Lugo-Lugo and B. Bilyeu, A review of chemical, electrochemical and biological methods for aqueous Cr (VI) reduction, *J. Hazard. Mater.*, 2012, **223**, 1–12.
- 5 K. Wenderich and G. Mul, Methods, mechanism, and applications of photodeposition in photocatalysis: a review, *Chem. Rev.*, 2016, **116**(23), 14587–14619.
- 6 S. Schrank, H. José and R. Moreira, Simultaneous photocatalytic Cr (VI) reduction and dye oxidation in a TiO<sub>2</sub> slurry reactor, *J. Photochem. Photobiol., A*, 2002, **147**(1), 71–76.
- 7 L. Wang, N. Wang, L. Zhu, H. Yu and H. Tang, Photocatalytic reduction of Cr (VI) over different TiO<sub>2</sub> photocatalysts and the effects of dissolved organic species, *J. Hazard. Mater.*, 2008, **152**(1), 93–99.
- 8 H. Kyung, J. Lee and W. Choi, Simultaneous and synergistic conversion of dyes and heavy metal ions in aqueous TiO<sub>2</sub> suspensions under visible-light illumination, *Environ. Sci. Technol.*, 2005, **39**(7), 2376–2382.
- 9 C. Dette, *et al.*, TiO<sub>2</sub> anatase with a bandgap in the visible region, *Nano Lett.*, 2014, **14**(11), 6533–6538.
- 10 X. Chen, *et al.*, Recent advances in titanium metal–organic frameworks and their derived materials: Features, fabrication, and photocatalytic applications, *Chem. Eng. J.*, 2020, **395**, 125080.
- 11 R. Lin, *et al.*, Facile generation of carbon quantum dots in MIL-53 (Fe) particles as localized electron acceptors for enhancing their photocatalytic Cr (vi) reduction, *Inorg. Chem. Front.*, 2018, **5**(12), 3170–3177.
- 12 D. Pattappan, S. Vargheese, K. Kavya, R. R. Kumar and Y. Haldorai, Metal-organic frameworks with different oxidation states of metal nodes and aminoterephthalic acid ligand for degradation of Rhodamine B under solar light, *Chemosphere*, 2022, **286**, 131726.
- 13 Y. Peng, V. Krungleviciute, I. Eryazici, J. T. Hupp, O. K. Farha and T. Yildirim, Methane Storage in Metal–Organic Frameworks: Current Records, Surprise Findings, and Challenges, *J. Am. Chem. Soc.*, 2013, **135**(32), 11887–11894.
- 14 T. M. McDonald, *et al.*, Cooperative insertion of CO<sub>2</sub> in diamine-appended metal-organic frameworks, *Nature*, 2015, **519**(7543), 303–308.





- 15 K. M. Park, H. Kim, J. Murray, J. Koo and K. Kim, A facile preparation method for nanosized MOFs as a multifunctional material for cellular imaging and drug delivery, *Supramol. Chem.*, 2017, **29**(6), 441–445.
- 16 L. T. Tran, H. T. Dang, H. V. Tran, G. T. Hoang and C. D. Huynh, MIL-88B (Fe)-NH<sub>2</sub>: an amine-functionalized metal-organic framework for application in a sensitive electrochemical sensor for Cd<sup>2+</sup>, Pb<sup>2+</sup>, and Cu<sup>2+</sup> ion detection, *RSC Adv.*, 2023, **13**(32), 21861–21872.
- 17 Y. Wen, M. Feng, P. Zhang, H.-C. Zhou, V. K. Sharma and X. Ma, Metal organic frameworks (MOFs) as photocatalysts for the degradation of agricultural pollutants in water, *ACS ES&T Eng.*, 2021, **1**(5), 804–826.
- 18 J. G. Santaclara, F. Kapteijn, J. Gascon and M. Van Der Veen, Understanding metal-organic frameworks for photocatalytic solar fuel production, *CrystEngComm*, 2017, **19**(29), 4118–4125.
- 19 L. Shao, Z. Yu, X. Li, X. Li, H. Zeng and X. Feng, Carbon nanodots anchored onto the metal-organic framework NH<sub>2</sub>-MIL-88B (Fe) as a novel visible light-driven photocatalyst: Photocatalytic performance and mechanism investigation, *Appl. Surf. Sci.*, 2020, **505**, 144616.
- 20 W.-T. Xu, *et al.*, Metal-organic frameworks MIL-88A hexagonal microrods as a new photocatalyst for efficient decolorization of methylene blue dye, *Dalton Trans.*, 2014, **43**(9), 3792–3798.
- 21 J.-J. Du, *et al.*, New photocatalysts based on MIL-53 metal-organic frameworks for the decolorization of methylene blue dye, *J. Hazard. Mater.*, 2011, **190**(1–3), 945–951.
- 22 R. Liang, L. Shen, F. Jing, N. Qin and L. Wu, Preparation of MIL-53 (Fe)-reduced graphene oxide nanocomposites by a simple self-assembly strategy for increasing interfacial contact: efficient visible-light photocatalysts, *ACS Appl. Mater. Interfaces*, 2015, **7**(18), 9507–9515.
- 23 J. Joseph, S. Iftekhhar, V. Srivastava, Z. Fallah, E. N. Zare and M. Sillanpää, Iron-based metal-organic framework: Synthesis, structure and current technologies for water reclamation with deep insight into framework integrity, *Chemosphere*, 2021, **284**, 131171.
- 24 L. Paseta, B. Seoane, D. Julve, V. Sebastián, C. Téllez and J. Coronas, Accelerating the Controlled Synthesis of Metal-Organic Frameworks by a Microfluidic Approach: A Nanoliter Continuous Reactor, *ACS Appl. Mater. Interfaces*, 2013, **5**(19), 9405–9410.
- 25 J. He, Y. Zhang, X. Zhang and Y. Huang, Highly efficient Fenton and enzyme-mimetic activities of NH<sub>2</sub>-MIL-88B (Fe) metal organic framework for methylene blue degradation, *Sci. Rep.*, 2018, **8**(1), 5159.
- 26 Y. Wang, *et al.*, Defect engineering of NH<sub>2</sub>-MIL-88B (Fe) using different monodentate ligands for enhancement of photo-Fenton catalytic performance of acetamiprid degradation, *Chem. Eng. J.*, 2020, **398**, 125684.
- 27 T. Van Tran, *et al.*, Effect of thermolysis condition on characteristics and nonsteroidal anti-inflammatory drugs (NSAIDs) absorbability of Fe-MIL-88B-derived mesoporous carbons, *J. Environ. Chem. Eng.*, 2019, **7**(5), 103356.
- 28 M. A. Yanuar and J. Kim, FeOF nanoparticles wrapped by graphitic carbon layers prepared from Fe-MIL-88B as a cathode material for sodium-ion batteries, *Carbon*, 2019, **149**, 483–491.
- 29 N. U. Saqib, R. Adnan and I. Shah, A mini-review on rare earth metal-doped TiO<sub>2</sub> for photocatalytic remediation of wastewater, *Environ. Sci. Pollut. Res.*, 2016, **23**, 15941–15951.
- 30 R. He, *et al.*, Design and synthesis of La<sup>3+</sup>, Sb<sup>3+</sup>-doped MOF-In<sub>2</sub>S<sub>3</sub>@FcDe-TAPT COFs hybrid materials with enhanced photocatalytic activity, *J. Mater. Sci.*, 2019, **54**, 14690–14706.
- 31 R. Kumar and H. Dosanjh, A mini-review on rare earth metal doped ZnO nanomaterials for photocatalytic remediation of waste water, *J. Phys.: Conf. Ser.*, 2022, **2267**(1), 012139.
- 32 S. Choi, W. Cha, H. Ji, D. Kim, H. J. Lee and M. Oh, Synthesis of hybrid metal-organic frameworks of {Fe<sub>x</sub>M<sub>y</sub>M'<sub>1-x-y</sub>}-MIL-88B and the use of anions to control their structural features, *Nanoscale*, 2016, **8**(37), 16743–16751.
- 33 F. Saraci, V. Quezada-Novoa, P. R. Donnarumma and A. J. Howarth, Rare-earth metal-organic frameworks: from structure to applications, *Chem. Soc. Rev.*, 2020, **49**(22), 7949–7977.
- 34 Y. Wang, *et al.*, Lanthanum and cesium-loaded SBA-15 catalysts for MMA synthesis by aldol condensation of methyl propionate and formaldehyde, *Catal. Lett.*, 2016, **146**, 1808–1818.
- 35 Z. Liu, Q. Wei, L. Qin, H. Shi and K. Shu, Growth and luminescence properties of Pr<sup>3+</sup>-doped LaCl<sub>3</sub> single crystal, *Funct. Mater. Lett.*, 2016, **9**(02), 1650022.
- 36 W. Adi, S. Wardiyati and S. Dewi, Nanoneedles of Lanthanum Oxide (La<sub>2</sub>O<sub>3</sub>): A Novel Functional Material for Microwave Absorber Material, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2017, **202**(1), 012066.
- 37 M. Ma, A. Bétard, I. Weber, N. S. Al-Hokbany, R. A. Fischer and N. Metzler-Nolte, Iron-Based Metal-Organic Frameworks MIL-88B and NH<sub>2</sub>-MIL-88B: High Quality Microwave Synthesis and Solvent-Induced Lattice “Breathing”, *Cryst. Growth Des.*, 2013, **13**(6), 2286–2291.
- 38 R. Yuan, C. Yue, J. Qiu, F. Liu and A. Li, Highly efficient sunlight-driven reduction of Cr(VI) by TiO<sub>2</sub>@NH<sub>2</sub>-MIL-88B (Fe) heterostructures under neutral conditions, *Appl. Catal., B*, 2019, **251**, 229–239.
- 39 Z. U. Zango, *et al.*, Removal of anthracene in water by MIL-88 (Fe), NH<sub>2</sub>-MIL-88 (Fe), and mixed-MIL-88 (Fe) metal-organic frameworks, *RSC Adv.*, 2019, **9**(71), 41490–41501.
- 40 H. Furukawa, *et al.*, Ultrahigh Porosity in Metal-Organic Frameworks, *Science*, 2010, **329**(5990), 424–428.
- 41 W.-J. Son, J. Kim, J. Kim and W.-S. Ahn, Sonochemical synthesis of MOF-5, *Chem. Commun.*, 2008, (47), 6336.
- 42 M. Pu, *et al.*, Synthesis of iron-based metal-organic framework MIL-53 as an efficient catalyst to activate persulfate for the degradation of Orange G in aqueous solution, *Appl. Catal., A*, 2018, **549**, 82–92.
- 43 T. T. Quang, N. X. Truong, T. H. Minh, N. N. Tue and G. T. P. Ly, Enhanced photocatalytic degradation of MB under visible light using the modified MIL-53 (Fe), *Top. Catal.*, 2020, **63**, 1227–1239.



- 44 X. Li, W. Guo, Z. Liu, R. Wang and H. Liu, Fe-based MOFs for efficient adsorption and degradation of acid orange 7 in aqueous solution via persulfate activation, *Appl. Surf. Sci.*, 2016, **369**, 130–136.
- 45 Y. Li, *et al.*, TiO<sub>2</sub> nanoparticles anchored onto the metal-organic framework NH<sub>2</sub>-MIL-88B (Fe) as an adsorptive photocatalyst with enhanced fenton-like degradation of organic pollutants under visible light irradiation, *ACS Sustain. Chem. Eng.*, 2018, **6**(12), 16186–16197.
- 46 L. Wang, *et al.*, Surface modification route to prepare novel polyamide@ NH<sub>2</sub>-MIL-88B nanocomposite membranes for water treatment, *RSC Adv.*, 2016, **6**(75), 71250–71261.
- 47 P. Makula, M. Pacia and W. Macyk, How to correctly determine the band gap energy of modified semiconductor photocatalysts based on UV-Vis spectra, *J. Phys. Chem. Lett.*, 2018, **9**, 6814–6817.
- 48 S. Deng, M. Duan, M. Xu and L. He, Effect of La doping on the electronic structure and optical properties of ZnO, *Phys. B*, 2011, **406**(11), 2314–2318.
- 49 J. Ungula, B. Dejene and H. Swart, Band gap engineering, enhanced morphology and photoluminescence of undoped, Ga and/or Al-doped ZnO nanoparticles by reflux precipitation method, *J. Lumin.*, 2018, **195**, 54–60.
- 50 Y.-R. Luo and J. A. Kerr, Bond dissociation energies, *CRC Handbook of Chemistry and Physics*, 2012, vol. 89, p. 89.
- 51 F. Kong and Y. Ni, Development of cellulosic paper-based test strips for Cr (VI) determination, *BioResources*, 2009, **4**(3), 1088–1097.
- 52 R. Liang, F. Jing, L. Shen, N. Qin and L. Wu, MIL-53 (Fe) as a highly efficient bifunctional photocatalyst for the simultaneous reduction of Cr (VI) and oxidation of dyes, *J. Hazard. Mater.*, 2015, **287**, 364–372.
- 53 H. Wang, *et al.*, Facile synthesis of amino-functionalized titanium metal-organic frameworks and their superior visible-light photocatalytic activity for Cr (VI) reduction, *J. Hazard. Mater.*, 2015, **286**, 187–194.
- 54 N. Unceta, F. Séby, J. Malherbe and O. F. X. Donard, Chromium speciation in solid matrices and regulation: a review, *Anal. Bioanal. Chem.*, 2010, **397**, 1097–1111.
- 55 H. Guo, *et al.*, Construction of direct Z-scheme AgI/Bi<sub>2</sub>Sn<sub>2</sub>O<sub>7</sub> nanojunction system with enhanced photocatalytic activity: accelerated interfacial charge transfer induced efficient Cr (VI) reduction, tetracycline degradation and *Escherichia coli* inactivation, *ACS Sustain. Chem. Eng.*, 2018, **6**(6), 8003–8018.
- 56 M.-L. Chen, T.-H. Lu, L.-L. Long, Z. Xu, L. Ding and Y.-H. Cheng, NH<sub>2</sub>-Fe-MILs for effective adsorption and Fenton-like degradation of imidacloprid: Removal performance and mechanism investigation, *Environ. Eng. Res.*, 2022, **27**(2), 200702.
- 57 C. Cheng, *Standard Redox Potential Table*, 2010.
- 58 L. Zhu, *et al.*, Performance enhancement of perovskite solar cells using a La-doped BaSnO<sub>3</sub> electron transport layer, *J. Mater. Chem. A*, 2017, **5**(7), 3675–3682.
- 59 S. Anandan, *et al.*, Photocatalytic degradation of 2, 4, 6-trichlorophenol using lanthanum doped ZnO in aqueous suspension, *Catal. Commun.*, 2007, **8**(9), 1377–1382.
- 60 C. Hu, Y.-C. Huang, A.-L. Chang and M. Nomura, Amine functionalized ZIF-8 as a visible-light-driven photocatalyst for Cr (VI) reduction, *J. Colloid Interface Sci.*, 2019, **553**, 372–381.
- 61 H. Zhao, Q. Xia, H. Xing, D. Chen and H. Wang, Construction of pillared-layer MOF as efficient visible-light photocatalysts for aqueous Cr (VI) reduction and dye degradation, *ACS Sustain. Chem. Eng.*, 2017, **5**(5), 4449–4456.
- 62 L. Shi, *et al.*, An amine-functionalized iron (III) metal-organic framework as efficient visible-light photocatalyst for Cr (VI) reduction, *Adv. Sci.*, 2015, **2**(3), 1500006.
- 63 H. Zhang, Y.-H. Luo, F.-Y. Chen, W.-Y. Geng, X.-X. Lu and D.-E. Zhang, Enhancing the spatial separation of photogenerated charges on Fe-based MOFs via structural regulation for highly-efficient photocatalytic Cr (VI) reduction, *J. Hazard. Mater.*, 2023, **441**, 129875.
- 64 Y. Nosaka and A. Nosaka, Understanding hydroxyl radical (•OH) generation processes in photocatalysis, *ACS Energy Lett.*, 2016, **1**(2), 356–359.
- 65 A. Lace, D. Ryan, M. Bowkett and J. Cleary, Chromium monitoring in water by colorimetry using optimised 1, 5-diphenylcarbazine method, *Int. J. Environ. Res. Public Health*, 2019, **16**(10), 1803.

