





Cite this: *RSC Adv.*, 2024, **14**, 25378

Chemical vapor deposition of hexagonal boron nitride on germanium from borazine†

Katherine A. Su, ^a Songying Li, ^a Wei-Chen Wen, ^b Yuji Yamamoto ^b
and Michael S. Arnold ^{*a}

The growth of hexagonal boron nitride (hBN) directly onto semiconducting substrates, like Ge and Ge on Si, promises to advance the integration of hBN into microelectronics. However, a detailed understanding of the growth and characteristics of hBN islands and monolayers on these substrates is lacking. Here, we present the growth of hBN on Ge and Ge epilayers on Si *via* high-vacuum chemical vapor deposition from borazine and study the effects of Ge sublimation, surface orientation, and vicinity on the shape and alignment of hBN islands. We find that suppressing Ge sublimation is essential for growing high quality hBN and that the Ge surface orientation and vicinity strongly affect hBN alignment. Interestingly, 95% of hBN islands are unidirectionally aligned on Ge(111), which may be a path toward metal- and transfer-free, single-crystalline hBN. Finally, we extend the growth time and borazine partial pressure to grow monolayer hBN on Ge and Ge epilayers on Si. These findings provide new insights into the growth of high-quality hBN on semiconducting substrates.

Received 20th May 2024
Accepted 6th August 2024

DOI: 10.1039/d4ra03704a

rsc.li/rsc-advances

Introduction

Hexagonal boron nitride (hBN) is a promising two-dimensional material for next generation electronics, due to its insulating properties, chemical inertness, and exotic optoelectronic behaviors. Chemical vapor deposition (CVD) onto catalytic substrates is the method of choice for the large-area production of mono- or few-layered hBN.¹ Typically, hBN is grown on metallic substrates, such as single-crystalline metal films^{2–7} and polycrystalline metal foils.⁸ However, hBN is rarely used as grown on metallic substrates. Instead, it is typically transferred to semiconducting or insulating wafer substrates through processes that invariably damage and contaminate the hBN. The direct growth of hBN on semiconducting substrates like Ge or Ge epilayers on Si could enable scalable, metal- and transfer-free integration of hBN into industrial processes and facilitate the manufacturing of devices using hBN-based heterostructures with other 2D materials,^{9–13} as well as hBN-based quantum emitters.^{14,15}

In previous work, hBN has been grown on Ge using two precursors, ammonia borane (AB)^{16,17} and borazine.¹⁸ Prior research^{16,17} has shown that hBN islands grown on Ge(001) and (110) *via* the low-pressure CVD of AB are highly aligned, with four observed island orientations on Ge(001) and two on

Ge(110). Other work¹⁸ has demonstrated the growth of multi-layer hBN *via* the high-vacuum CVD of borazine onto Ge epilayers on Si(001). While AB is generally viewed as a safer precursor, it is a solid with a low vapor pressure and is complicated to control. Primarily, AB must be heated to release vapor. However, AB has been found to release seven different N and B-containing species with non-correlated flow profiles that vary with time. These species ultimately form hBN deposits with different nucleation densities, growth rates, and morphologies unless the AB temperature is adjusted throughout growth to maintain a constant ratio of B and N feedstock.¹⁹ All of these factors further complicate achieving a precise and stable precursor partial pressure and the controllable growth of hBN. Borazine, while challenged by its flammability and air-sensitivity, is a liquid at room temperature with a high vapor pressure whose partial pressure can be controlled reproducibly through more straightforward means. For example, borazine can be leaked into a high-vacuum CVD system with leak valves⁶ or controlled with a carrier gas bubbler and mass flow controller.²⁰

In this work, we present the growth of high-quality hBN islands and monolayers on single-crystalline Ge and Ge epitaxial layers on Si *via* high-vacuum CVD with borazine as the precursor. We investigate Ge sublimation under high-vacuum and its impact on hBN nucleation and morphology. We also explore the influence of Ge surface orientation and vicinity on hBN island alignment, learning that hBN islands are nearly unidirectionally aligned on Ge(111). Additionally, we describe a method for reducing pinhole density in hBN monolayers. Finally, we grow hBN on Ge epitaxial layers on Si, overcoming

^aDepartment of Materials Science and Engineering, University of Wisconsin-Madison, Madison, Wisconsin 53706, USA. E-mail: michael.arnold@wisc.edu

^bIHP-Leibniz-Institut für Innovative Mikroelektronik, Im Technologiepark 25, 15236 Frankfurt (Oder), Germany

† Electronic supplementary information (ESI) available: Additional SEM/AFM data and schematics. See DOI: <https://doi.org/10.1039/d4ra03704a>


challenges associated with the diffusion of noncatalytic Si to the growth surface and demonstrating the compatibility of this process with commercially relevant substrates.

Experimental

Growth of hBN *via* chemical vapor deposition

hBN is grown from borazine *via* high-vacuum CVD. The CVD system consists of a quartz tube surrounded by a three-zone tube furnace on a linear track, which facilitates the furnace's movement along the length of the tube. The tube has an inner diameter of 34 mm and a heated zone of 30 cm. The downstream end of the tube is equipped with a turbopump and residual gas analyzer (RGA, Stanford Research Systems, RGA 200). Approximately 5 mL of borazine precursor (CAS No. 6569-51-3, Gelest) is transferred from the commercial bottle to a domed Pyrex tube. The tube is connected to the pump with a bellows sealed valve and to the CVD system with a variable leak valve, similar to the setup used by Arias *et al.*⁶ Precautions should be taken to avoid borazine exposure, as it is classified as causing GHS category 1B skin corrosion/irritation and category 1 serious eye damage/irritation.

hBN is grown on single-crystalline Ge(001), (110), and (111) (AXT, Ga dopants, electrical resistivity < 0.05 Ω cm); single-crystalline Ge(001) intentionally miscut by 6 and 9° toward Ge [111] (University Wafer, Ga dopants, 0.01–0.05 Ω cm); and 3 μ m-thick Ge epilayers on Si(001), (110), and (111). The Ge epilayers on Si are fabricated *via* reduced-pressure CVD. A threading dislocation density of $\sim 1 \times 10^7$ cm⁻² is achieved using a cyclical annealing process, as described by Yamamoto *et al.*^{21–23} The substrates are cleaved into 0.8 cm pieces and positioned polished-side-down on a Ge(001) base.

After loading the substrates, the system is pumped down and then refilled with Ar and H₂ to atmospheric pressure. The gas flow is changed to 200 sccm Ar and 100 sccm H₂ and allowed to equilibrate for 10 minutes. Then, with Ar and H₂ still flowing, the furnace is slid over the samples to anneal them for 45 minutes at 920 °C to remove Ge oxides and organic adsorbates. Simultaneously, the borazine precursor is purified *via* three freeze–pump–thaw cycles (see ESI Note 1† for details). Without cooling the samples, Ar and H₂ flow are stopped, and the system is pumped down to less than 1×10^{-5} torr within 10 minutes. For hBN growth, borazine is leaked into the system at the desired partial pressure measured with the RGA for the desired amount of time. After growth, the furnace is slid away from the samples, and the samples are cooled to room temperature.

Transfer of hBN to SiO₂/Si

hBN monolayers are transferred to 90 nm of SiO₂ on Si for Raman spectroscopy and X-ray photoelectron spectroscopy (XPS). This process involves spin-coating C7 PMMA onto the samples at 2000 rpm for 1 minute, annealing them in N₂ at 160 °C for 5 minutes, and scratching the sample edges with a razor blade. Delamination of PMMA/hBN from the growth substrate is achieved electrochemically.^{2,24} Specifically, we fabricate an electrochemical cell consisting of 1 M NaOH as the electrolyte,

Pt foil as the anode, the sample as the cathode, and a 9 V battery. After delaminating, the films are transferred to cleaned SiO₂/Si substrates, and the PMMA is removed *via* acetone soaking followed by high-vacuum annealing.

Characterization

To characterize hBN morphology and topography, we use scanning electron microscopy (SEM, Zeiss GeminiSEM 450) and atomic force microscopy (AFM, Bruker Dimension Icon AFM). To characterize transferred hBN films, we use Raman spectroscopy (Horiba LabRAM HR Evolution Raman Spectrometer) with an excitation wavelength of 532 nm, 25 mW laser power, and 1800 mm⁻¹ grating. We also measure the stoichiometry of the transferred films with XPS (Thermo K alpha X-ray Photoelectron Spectrometer) equipped with a monochromated Al K α X-ray source with a spot size of 400 μ m and a flood gun to mitigate surface charging. Peak positions are calibrated using the Si 2p peak of the SiO₂/Si substrate at 103.5 eV. Vendor-adjusted Scofield relative sensitivity factors are used to calculate B : N atomic ratios.

To measure the density of pinhole defects, we dip the samples as grown into 0.02 M FeCl₃ for 1 minute and triple rinse in deionized water. The FeCl₃ diffuses through pinholes in hBN, creating etch pits in the Ge that can then be measured with AFM. To reveal threading dislocations that are present in Ge on Si(001), we dip the samples into Secco etch solution, a mixture of one part 0.15 M potassium dichromate (K₂Cr₂O₇) in water to two parts 49% HF, for 1 minute.²⁵ Note, the GHS category 1 corrosive, carcinogenic, mutagenic, and toxic chemical, K₂Cr₂O₇, and the category 1 corrosive and toxic chemical, HF, pose significant safety hazards and must be handled with extreme care.

Results and discussion

The importance of suppressing Ge sublimation

First, we find that suppressing Ge sublimation, which occurs readily under high vacuum at the growth temperature of 920 °C, is crucial for growing high-quality hBN. In Fig. 1, we compare two different substrate configurations: a face-up configuration, in which the growth surface is exposed to high vacuum (Fig. 1a), and a face-to-face configuration, in which the growth surface is placed in direct contact with another piece of Ge (Fig. 1b).

When Ge(001) is annealed under high vacuum in the face-up configuration, Ge sublimates, and the surface roughens considerably (Fig. 1c, RMS roughness = 5.6 nm). The roughening of the surface results in a high hBN nucleation density, non-triangular morphology, and non-uniform thickness of hBN islands grown in this configuration (Fig. 1d). These results may explain the high nucleation density observed for multilayer hBN grown on Ge on Si(001) from borazine *via* high-vacuum CVD reported previously.¹⁸ Additionally, thermal etch pits that are over 1 μ m deep form after just 30 minutes of annealing (Fig. S1†). These pits would interfere significantly with the growth and coalescence of a monolayer of hBN. In contrast, when Ge(001) is annealed under high vacuum in the face-to-face configuration, the surface is significantly smoother (Fig. 1e,



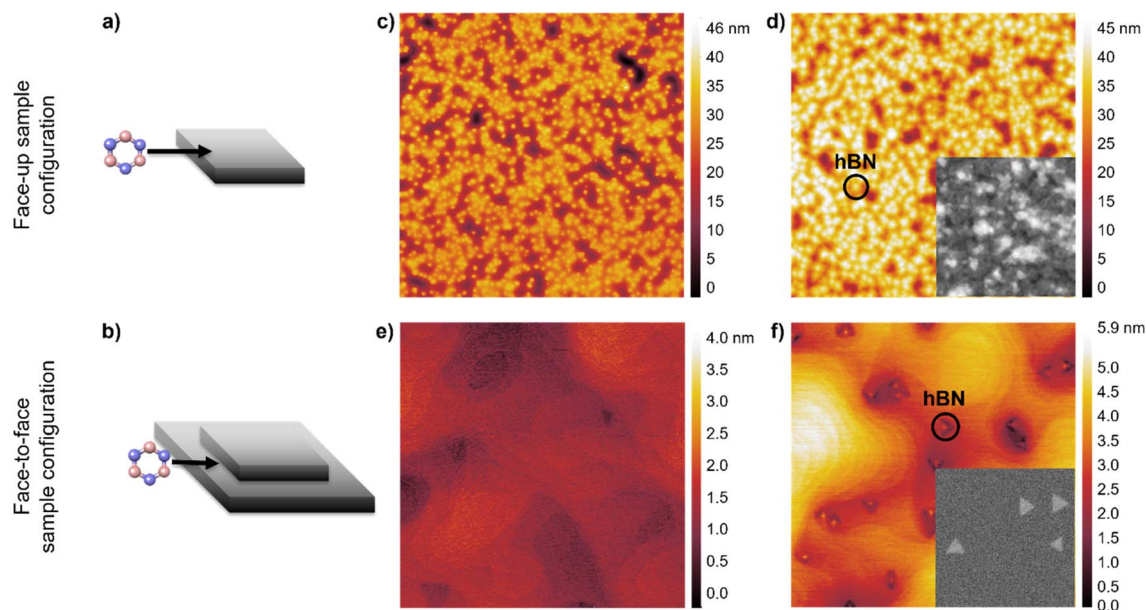


Fig. 1 Schematics illustrating the (a) face-up and (b) face-to-face sample configurations. AFM height maps showing the morphology of the Ge(001) surface after high-vacuum annealing for 30 min at 920 °C in the (c) face-up and (e) face-to-face configurations and after growth of hBN islands with a borazine partial pressure of 1×10^{-10} torr for 30 min at 920 °C in the (d) face-up and (f) face-to-face configurations. All AFM maps are $5 \mu\text{m} \times 5 \mu\text{m}$. Insets in (d) and (f) show enlarged SEM of hBN islands from the same samples.

RMS roughness = 0.3 nm). We attribute this smoothness to the suppression of Ge sublimation due to the buildup of Ge vapor pressure between the two faces. hBN islands grown in this configuration have lower nucleation density and triangular morphology (Fig. 1f), indicating marked improvement over hBN grown in the face-up configuration.

The effect of Ge surface orientation on hBN island orientation

Using a face-to-face configuration, a borazine partial pressure of 1×10^{-10} torr, and a growth time of 30 minutes, we grow hBN islands on Ge(001), (110), and (111), as well as Ge(001) intentionally miscut by 6° and 9° toward Ge[111] and show that hBN island orientations are highly dependent on the Ge surface orientation. We use a low borazine partial pressure of 1×10^{-10} torr because the resulting slow growth rate (~ 100 to 200 nm min^{-1}) and low nucleation density (~ 1 to $2 \mu\text{m}^{-2}$) result in triangular, mostly non-overlapping islands whose orientations can be easily observed and quantified using SEM. Prior work by Yin *et al.* indicates that hBN edges on Ge(001) and (110) are aligned along the zigzag direction.¹⁶ We anticipate hBN edges to be N-terminated based on theoretical predictions by Zhang *et al.* for hBN on Cu and Ni,²⁶ which are weakly interacting catalysts like Ge. Fig. 2a shows SEM of the hBN islands, and Fig. 2b shows AFM height maps of the same samples as in Fig. 2a, indicating that the Ge(110) and (111) surfaces are significantly smoother than the (001) surface after the growth of hBN islands.

On Ge(001), (001)- 6° , and (001)- 9° , hBN islands are triangular and have four preferred orientations, each having an edge parallel to Ge[110] or $[\bar{1}\bar{1}0]$ (Fig. 2a–c). When the miscut angle is approximately 0° , the islands are distributed evenly between the four preferred orientations, as previously reported by Yin *et al.*¹⁶ When the miscut angle is increased to 6° and then 9° , the

distribution shifts such that orientations where the island edge is parallel to Ge[110] are preferred, with an increasing preference for the islands to be pointed downhill (Fig. 2d). This is likely due to the preferential nucleation of hBN islands off of Ge step edges in the downhill direction. Ultimately, it may be possible to grow unidirectionally aligned hBN islands by increasing the miscut angle further.

On Ge(110), hBN islands have two preferred orientations, each having an edge parallel to Ge $[\bar{1}\bar{1}0]$, similar to the observations made by Yin *et al.* and Zhang *et al.*^{16,17} The islands are distributed approximately evenly between the two preferred orientations (Fig. 2d), which is expected on the two-fold symmetrical Ge(110) surface.

On Ge(111), triangular hBN islands are expected to have six (or two unique) preferred orientations due to the six-fold symmetry of the Ge(111) surface. However, we observe that one of the two unique orientations is heavily favored, and 95% of the islands are unidirectionally aligned (Fig. 1a–d). This unexpected result may be explained by a theory proposed by Chen *et al.*, in which asymmetry at opposing Cu(111) step edges and in their binding energies causes hBN nuclei to dock preferentially on one side of the steps, resulting in the unidirectional alignment of hBN islands on Cu(111).² A similar asymmetry at opposing step edges is seen on Ge(111) (Fig. S2†), which seems to have the same effect as on Cu(111). With further tuning of growth parameters and understanding of hBN nuclei-step docking on Ge, it may be possible to grow single crystal hBN on Ge(111).

Growth and characterization of hBN monolayers on single-crystalline Ge

By extending the growth time from 30 minutes to 10 hours, we are able to grow monolayer hBN on Ge(001), (110), and (111).



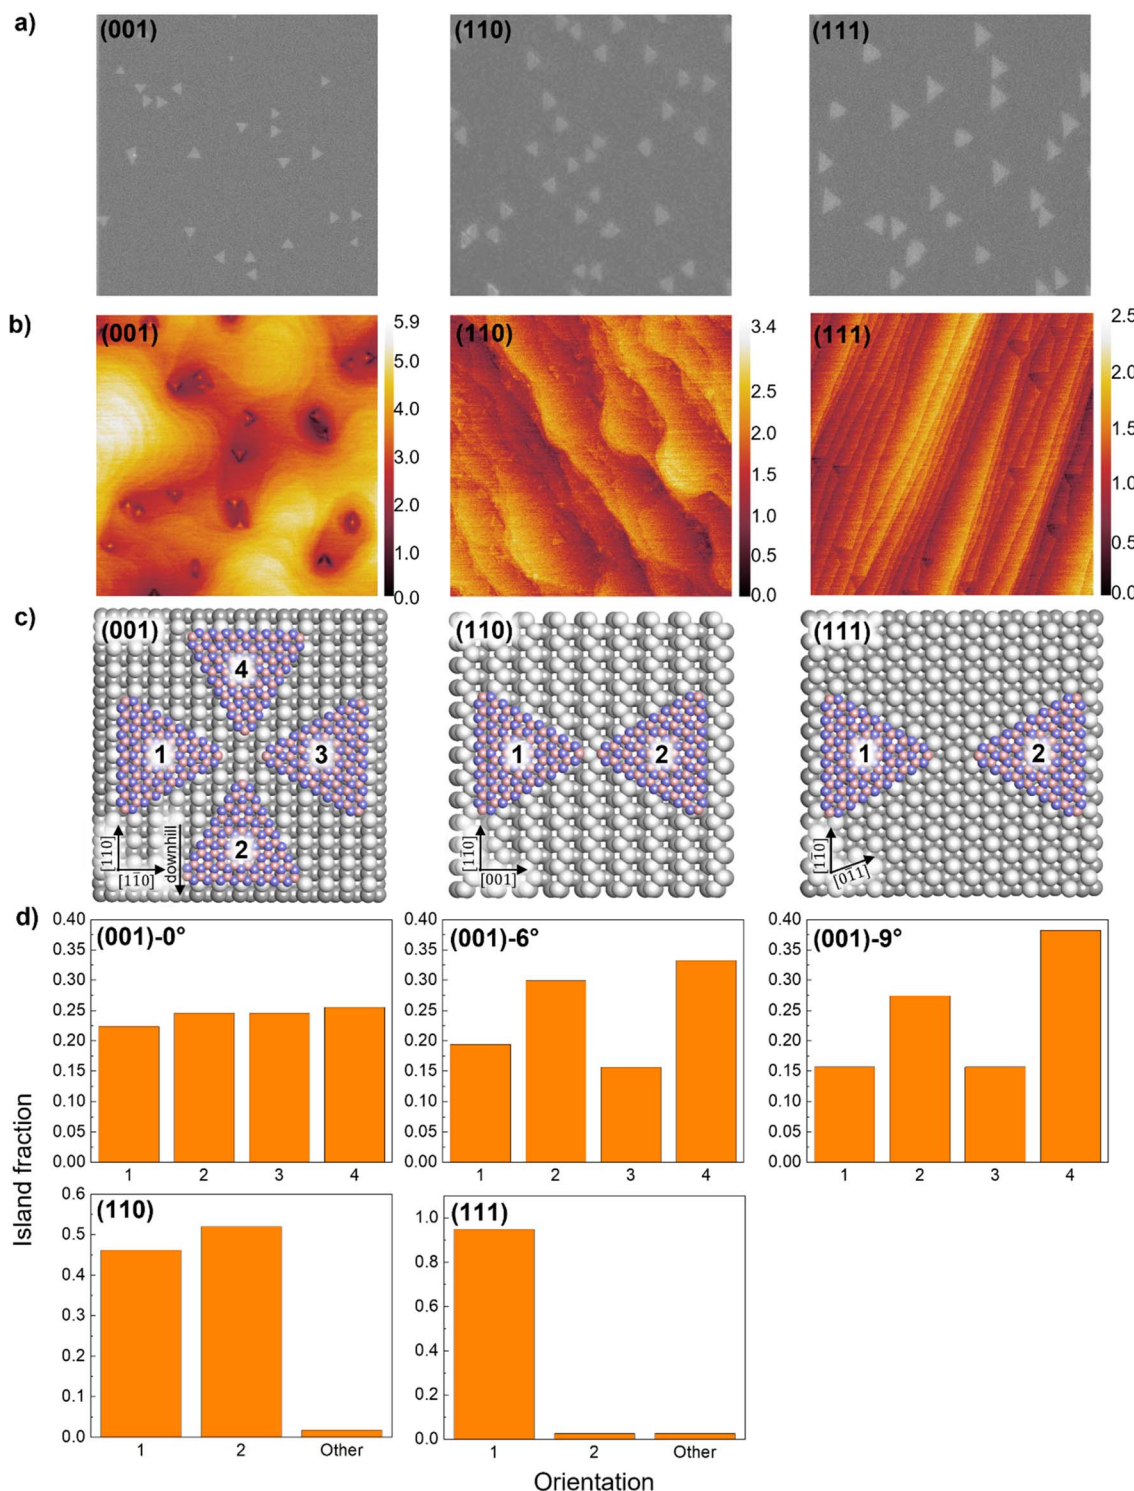


Fig. 2 (a) SEM images and (b) AFM height maps of hBN islands grown on Ge(001), (110), and (111). (c) Schematics showing preferred hBN island orientations. (d) Bar graphs showing the fraction of islands oriented within $\pm 2^\circ$ of a preferred orientation on Ge(001), (001)-6°, (001)-9°, (110), and (111). All samples are grown with a borazine partial pressure of 1×10^{-10} torr and growth time of 30 min. SEM images and AFM maps are $5 \mu\text{m} \times 5 \mu\text{m}$. AFM scale bars are in nm. Arrows in (c) depict crystallographic directions and the downhill direction for vicinal Ge(001). Edge termination and lateral position of hBN in schematics in (c) are not confirmed experimentally. Number of islands measured in (d) is 505, 608, 536, 710, and 1020 for Ge(001), (001)-6°, (001)-9°, (110), and (111), respectively.

Wrinkles originating from the difference in the coefficient of thermal expansion of hBN and Ge are seen in SEM (Fig. 3a) and AFM (Fig. 3b), indicating that the surface is fully covered. In

addition, AFM shows that after hBN growth, the Ge(110) and (111) surfaces are atomically flat, but the Ge(001) surface is nano-faceted (Fig. 3b). As a result, hBN grown on Ge(110) and

© 2024 The Author(s). Published by the Royal Society of Chemistry

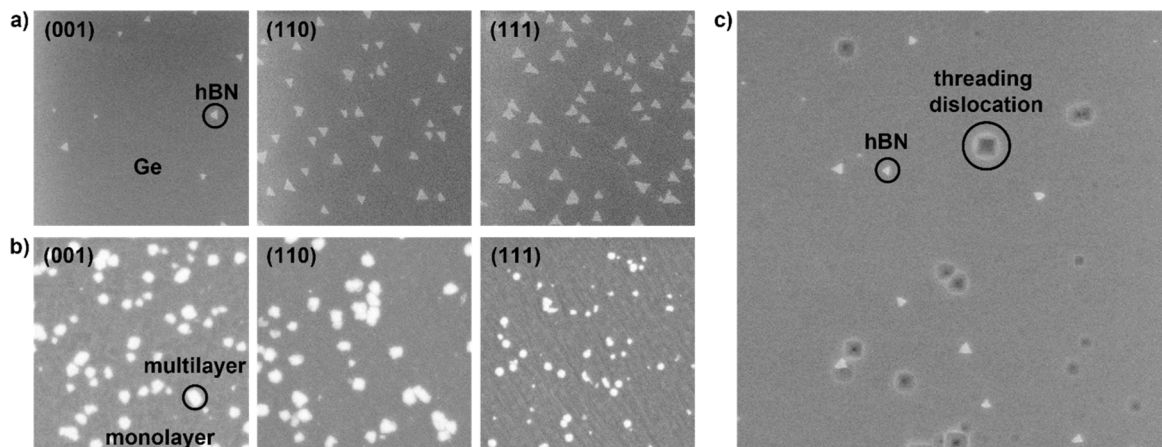


Fig. 5 SEM images of (a) hBN islands and (b) hBN monolayers with multilayer islands grown on Ge/Si(001), (110), and (111). (c) SEM showing lack of correlation between hBN island nucleation and threading dislocations (revealed with a 1 min Secco etch) on Ge/Si(001). The islands in (a) and (c) are grown with a borazine partial pressure of 1×10^{-10} torr for 30 min. The monolayers in (b) are grown with a borazine partial pressure of 6×10^{-10} torr for 6 h. SEM images are $5 \mu\text{m} \times 5 \mu\text{m}$ in (a) and (b) and $10 \mu\text{m} \times 10 \mu\text{m}$ in (c).

rotational alignment and similar morphology to islands grown on equivalent Ge surfaces, indicating that growth is comparable on the two substrates (Fig. 5a). However, small differences in the hBN island morphology specifically on Ge/Si(111) are observed, possibly due to the high initial roughness of the Ge/Si(111) surface (Fig. S6†). Additionally, we dip the hBN islands grown on Ge/Si(001) into Secco etch solution, which selectively creates etch pits at threading dislocations in the Ge epilayer.²⁵ We find that the location of these threading dislocations has no correlation with where hBN islands nucleate (Fig. 5c).

The growth of monolayer hBN is complicated by the diffusion of Si through Ge at high temperatures. When Si segregates at the Ge surface, it roughens the surface³⁴ and disrupts hBN growth, likely due to its noncatalytic nature and requirements for higher growth temperatures³⁵ (Fig. S7†). To minimize Si diffusion, we increase the borazine partial pressure from 1×10^{-10} to 6×10^{-10} torr so that growth can be completed within 6 hours instead of 10. While this does enable faster coalescence, we also observe the formation of multilayer hBN islands, with coverage ranging from 2 to 5% and heights ranging from 1 to 8 nm (Fig. 5b).

Conclusions

In summary, suppressing Ge sublimation is essential for growing high-quality hBN on Ge *via* high-vacuum CVD. Using a borazine precursor, we show that the orientational alignment of hBN correlates strongly with the surface orientation and miscut angle of Ge. Remarkably, 95% of hBN nuclei are unidirectionally aligned on Ge(111), which presents a promising path toward the growth of single-crystalline hBN on a semi-conducting substrate. Despite hBN monolayers appearing to be full coverage and high quality as characterized by SEM, AFM, and Raman spectroscopy, pinhole defects can be prevalent. However, the density of pinhole defects can be significantly reduced by introducing a burst of borazine precursor toward the

end of the hBN growth process. These findings, along with successful hBN growth on Ge epitaxial layers on Si, hold considerable promise for the integration of hBN into advanced microelectronics.

Data availability

The data supporting this article have been included within the manuscript and electronic ESI.†

Author contributions

KAS: conceptualization, methodology, investigation, and writing – original draft. SL: methodology and validation. WCW: resources. YY: resources and writing – review and editing. MSA: conceptualization, writing – review and editing, supervision, and funding acquisition.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

Investigation of Ge orientation dependence, growth on Ge epilayers on Si, Raman spectroscopy, XPS, and etch pit characterization supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, under Grant No. DE-SC0016007 (K. A. S., M. S. A.). Early studies on effects of Ge sublimation, XPS, and CVD tool development supported by the U.S. National Science Foundation Grant No. DMR-2102643 (S. L., M. S. A.). The authors acknowledge the use of facilities and instrumentation at the UW-Madison Wisconsin Centers for Nanoscale Technology, which is partially supported by the NSF through the University of Wisconsin Materials Research Science and Engineering Center (DMR-1720415). Support from a U.S. NSF Graduate Research Fellowship under Grant No. DGE-1747503

and from a PPG Industries Graduate Fellowship is also acknowledged (K. A. S.).

References

- 1 N. Briggs, S. Subramanian, Z. Lin, X. Li, X. Zhang, K. Zhang, K. Xiao, D. Geohagan, R. Wallace, L.-Q. Chen, M. Terrones, A. Ebrahimi, S. Das, J. Redwing, C. Hinkle, K. Momeni, A. Van Duin, V. Crespi, S. Kar and J. A. Robinson, *2D Mater.*, 2019, **6**, 022001.
- 2 T. A. Chen, C. P. Chuu, C. C. Tseng, C. K. Wen, H. S. P. Wong, S. Pan, R. Li, T. A. Chao, W. C. Chueh, Y. Zhang, Q. Fu, B. I. Yakobson, W. H. Chang and L. J. Li, *Nature*, 2020, **579**, 219–223.
- 3 L. Wang, X. Xu, L. Zhang, R. Qiao, M. Wu, Z. Wang, S. Zhang, J. Liang, Z. Zhang, Z. Zhang, W. Chen, X. Xie, J. Zong, Y. Shan, Y. Guo, M. Willinger, H. Wu, Q. Li, W. Wang, P. Gao, S. Wu, Y. Zhang, Y. Jiang, D. Yu, E. Wang, X. Bai, Z. J. Wang, F. Ding and K. Liu, *Nature*, 2019, **570**, 91–95.
- 4 S. Joshi, D. Eciija, R. Koitz, M. Iannuzzi, A. P. Seitsonen, J. Hutter, H. Sachdev, S. Vijayaraghavan, F. Bischoff, K. Seufert, J. V. Barth and W. Auwärter, *Nano Lett.*, 2012, **12**, 5821–5828.
- 5 X. Song, J. Gao, Y. Nie, T. Gao, J. Sun, D. Ma, Q. Li, Y. Chen, C. Jin, A. Bachmatiuk, M. H. Rummeli, F. Ding, Y. Zhang and Z. Liu, *Nano Res.*, 2015, **8**, 3164–3176.
- 6 P. Arias, A. Ebnonnasir, C. V. Ciobanu and S. Kodambaka, *Nano Lett.*, 2020, **20**, 2886–2891.
- 7 Y. Uchida, T. Iwaizako, S. Mizuno, M. Tsuji and H. Ago, *Phys. Chem. Chem. Phys.*, 2017, **19**, 8230–8235.
- 8 K. K. Kim, A. Hsu, X. Jia, S. M. Kim, Y. Shi, M. Hofmann, D. Nezich, J. F. Rodriguez-Nieva, M. Dresselhaus, T. Palacios and J. Kong, *Nano Lett.*, 2012, **12**, 161–166.
- 9 M. P. Levendorf, C.-J. Kim, L. Brown, P. Y. Huang, R. W. Havener, D. A. Muller and J. Park, *Nature*, 2012, **488**, 627–632.
- 10 S. Wang, X. Wang and J. H. Warner, *ACS Nano*, 2015, **9**, 5246–5254.
- 11 A. Yan, J. Jr. Velasco, S. Kahn, K. Watanabe, T. Taniguchi, F. Wang, M. F. Crommie and A. Zettl, *Nano Lett.*, 2015, **15**, 6324–6331.
- 12 M. Okada, T. Sawazaki, K. Watanabe, T. Taniguchi, H. Hibino, H. Shinohara and R. Kitaura, *ACS Nano*, 2014, **8**, 8273–8277.
- 13 M. Alahmadi, F. Mahvash, T. Szkopek and M. Siaj, *RSC Adv.*, 2021, **11**, 16962–16969.
- 14 S. J. U. White, T. Yang, N. Donschuk, C. Li, Z.-Q. Xu, M. Kianinia, A. Stacey, M. Toth and I. Aharonovich, *Light: Sci. Appl.*, 2022, **11**, 186.
- 15 N. Chejanovsky, A. Mukherjee, J. Geng, Y.-C. Chen, Y. Kim, A. Denisenko, A. Finkler, T. Taniguchi, K. Watanabe, D. B. R. Dasari, P. Auburger, A. Gali, J. H. Smet and J. Wrachtrup, *Nat. Mater.*, 2021, **20**, 1079–1084.
- 16 J. Yin, X. Liu, W. Lu, J. Li, Y. Cao, Y. Li, Y. Xu, X. Li, J. Zhou, C. Jin and W. Guo, *Small*, 2015, **11**, 5375–5380.
- 17 C. Zhang, B. Gao, Y. Ran, Z. Shi, H. Zhu, H. Zhang, J. Liu, B. Yang, Z. Liu, T. Wu and X. Xie, *2D Mater.*, 2021, **8**, 035041.
- 18 M. Franck, J. Dabrowski, M. A. Schubert, C. Wenger and M. Lukosius, *Nanomaterials*, 2022, **12**, 3260.
- 19 V. Babenko, G. Lane, A. A. Koos, A. T. Murdock, K. So, J. Britton, S. S. Meysami, J. Moffat and N. Grobert, *Sci. Rep.*, 2017, **7**, 14297.
- 20 J. H. Park, A. Y. Lu, M. M. Tavakoli, N. Y. Kim, M. H. Chiu, H. Liu, T. Zhang, Z. Wang, J. Wang, L. G. P. Martins, Z. Luo, M. Chi, J. Miao and J. Kong, *Nano Lett.*, 2023, **23**, 4741–4748.
- 21 Y. Yamamoto, P. Zaumseil, T. Arguirov, M. Kittler and B. Tillack, *Solid-State Electron.*, 2011, **60**, 2–6.
- 22 Y. Yamamoto, P. Zaumseil, M. A. Schubert and B. Tillack, *Semicond. Sci. Technol.*, 2018, **33**, 124007.
- 23 Y. Yamamoto, W. C. Wen, M. A. Schubert, C. Corley-Wiciak and B. Tillack, *ECS J. Solid State Sci. Technol.*, 2023, **12**, 023014.
- 24 L. Gao, W. Ren, H. Xu, L. Jin, Z. Wang, T. Ma, L. P. Ma, Z. Zhang, Q. Fu, L. M. Peng, X. Bao and H. M. Cheng, *Nat. Commun.*, 2012, **3**, 699.
- 25 A. Abbadie, F. Allibert and F. Brunier, *Solid-State Electron.*, 2009, **53**, 850–857.
- 26 Z. Zhang, Y. Liu, Y. Yang and B. I. Yakobson, *Nano Lett.*, 2016, **16**, 1398–1403.
- 27 R. M. Jacobberger, D. E. Savage, X. Zheng, P. Sookchoo, R. Rojas Delgado, M. G. Lagally and M. S. Arnold, *Chem. Mater.*, 2022, **34**, 6769–6778.
- 28 H. Arora, Y. Jung, T. Venanzi, K. Watanabe, T. Taniguchi, R. Hübner, H. Schneider, M. Helm, J. C. Hone and A. Erbe, *ACS Appl. Mater. Interfaces*, 2019, **11**, 43480–43487.
- 29 A. J. Cho and J. Y. Kwon, *ACS Appl. Mater. Interfaces*, 2019, **11**, 39765–39771.
- 30 C. R. Dean, A. F. Young, I. Meric, L. Wang, S. Sorgenfrei, K. Watanabe, T. Taniguchi, P. Kim, K. L. Shepard and J. Hone, *Nat. Nanotechnol.*, 2010, **5**, 722–726.
- 31 N. Fang, K. Otsuka, A. Ishii, T. Taniguchi, K. Watanabe, K. Nagashio and Y. K. Kato, *ACS Photonics*, 2020, **7**, 1773–1779.
- 32 E. V. Calman, M. M. Fogler, L. V. Butov, S. Hu, A. Mishchenko and A. K. Geim, *Nat. Commun.*, 2018, **9**, 1895.
- 33 R. M. Jacobberger, M. J. Dodd, M. Zamiri, A. J. Way, M. S. Arnold and M. G. Lagally, *ACS Appl. Nano Mater.*, 2019, **2**, 4313–4322.
- 34 V. Saraswat, Y. Yamamoto, H. J. Kim, R. M. Jacobberger, K. R. Jinkins, A. J. Way, N. P. Guisinger and M. S. Arnold, *J. Phys. Chem. C*, 2019, **123**, 18445–18454.
- 35 X. Chen, C. Tan, X. Liu, K. Luan, Y. Guan, X. Liu, J. Zhao, L. Hou, Y. Gao and Z. Chen, *J. Mater. Sci.: Mater. Electron.*, 2021, **32**, 3713–3719.

