

Cite this: *Chem. Sci.*, 2024, 15, 3262

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Elastic MXene conductive layers and electrolyte engineering enable robust potassium storage†

Xinyue Xu,<sup>‡a</sup> Qingqing Jiang,<sup>‡a</sup> Chenyu Yang,<sup>‡b</sup> Jinxi Ruan,<sup>b</sup> Weifang Zhao,<sup>a</sup> Houyu Wang,<sup>b</sup> Xinxin Lu,<sup>b</sup> Zhe Li,<sup>‡a</sup> Yuanzhen Chen,<sup>c</sup> Chaofeng Zhang,<sup>‡\*b</sup> Juncheng Hu,<sup>‡\*a</sup> and Tengfei Zhou<sup>‡\*b</sup>

The precisely engineered structures of materials greatly influence the manifestation of their properties. For example, in the process of alkali metal ion storage, a carefully designed structure capable of accommodating inserted and extracted ions will improve the stability of material cycling. The present study explores the uniform distribution of self-grown carbon nanotubes to provide structural support for the conductive and elastic MXene layers of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ . Furthermore, a compatible electrolyte system has been optimized by analyzing the solvation structure and carefully regulating the component in the solid electrolyte interphase (SEI) layer. Mechanistic studies demonstrate that the decomposition predominantly controlled by  $\text{FSI}^-$  leads to the formation of a robust inorganic SEI layer enriched with KF, thus effectively inhibiting irreversible side reactions and major structural deterioration. Confirming our expectations,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  exhibits an impressive reversible capacity of  $260 \text{ mA h g}^{-1}$ , even after 2000 cycles at  $500 \text{ mA g}^{-1}$  in 1 M KFSI (DME), surpassing most MXene-based anodes reported for PIBs. Additionally, density functional theory (DFT) calculations verify the superior electronic conductivity and lower  $\text{K}^+$  diffusion energy barriers of the novel superstructure of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , thereby affirming the improved electrochemical kinetics. This study presents systematic evaluation methodologies for future research on MXene-based anodes in PIBs.

Received 13th November 2023  
Accepted 17th January 2024

DOI: 10.1039/d3sc06079a

rsc.li/chemical-science

## Introduction

Potassium-ion batteries (PIBs) are increasingly regarded as a prospective substitute for lithium-ion batteries (LIBs) for large-scale energy storage systems owing to plentiful potassium resources, lower redox potential, and smaller solvation radius.<sup>1</sup> Nonetheless, the large size of potassium ions and the resulting high repulsive forces lead to structural damage and slow kinetics during repeated intercalation/deintercalation processes, significantly restricting their applicability.<sup>2</sup> Consequently, there is a requirement to design high-performance electrode materials with sturdy structures capable of accommodating  $\text{K}^+$  ions, thereby enhancing rate capability and cycle life.

MXenes, which are transition metal carbides/nitrides, possess inherently prime conductivity, mechanical flexibility, and adjustable layer spacing, all of which are extremely desirable for PIBs.<sup>3</sup> However, both theoretical and experimental studies confirm that pristine MXenes exhibit low potassium storage capabilities and experience rapid capacity decay owing to susceptible self-aggregation caused by van der Waals interactions or hydrogen bonds between adjacent exfoliated layers.<sup>4</sup> The irreversibility of restacking or spontaneous collapse greatly restricts the optimum utilization of MXene-based electrode materials. Therefore, the design of heterostructures is essential to effectively preventing the aggregation or self-restacking of MXene nanosheets in electrochemical energy storage applications.<sup>5</sup> Due to their high electrical conductivity and rapid potassium transfer properties,  $\text{Ti}_3\text{C}_2\text{T}_x$  nanosheets are better suited for constructing an electrode framework that ensures fast electron and ion transfer, rather than serving as active materials.<sup>6</sup>

Carbon nanotubes (CNTs) with high electrical conductivity have been used as the embedding spacer to prevent the restacking of MXene sheets.<sup>7</sup> Unfortunately, the *ex situ* mixing growth method often suffers from disordered dispersion of CNTs and high contact resistance. It is widely acknowledged that vertically aligned arrays of CNTs show great promise as electrical contacts.<sup>8</sup> Consequently, various methods have been explored for the *in situ* growth of highly integrated CNTs

<sup>a</sup>Key Laboratory of Catalysis and Energy Materials Chemistry of Ministry of Education, South-Central Minzu University, Wuhan 430074, China. E-mail: qqjiang@mail.scuec.edu.cn; jchu@mail.scuec.edu.cn

<sup>b</sup>Institutes of Physical Science and Information Technology, Key Laboratory of Structure and Functional Regulation of Hybrid Material (Ministry of Education), Anhui University, Hefei 230601, China. E-mail: cfz@ahu.edu.cn; tengfeiz@ahu.edu.cn

<sup>c</sup>State Key Laboratory for Mechanical Behavior of Materials, School of Materials Science and Engineering, Xi'an Jiaotong University, Xi'an, 710049, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc06079a>

‡ These authors contributed equally.

between  $\text{Ti}_3\text{C}_2\text{T}_x$  layers, including chemical vapor deposition, hydrothermal reaction, microwave irradiation, and high-temperature pyrolysis treatment.<sup>9</sup> Moreover, CNTs can be further enhanced through heteroatom doping, such as the introduction of transition metal active sites or incorporating n sites, which alters the charge density of carbon atoms, provides additional active sites, and improves overall conductivity.<sup>10</sup> Drawing inspiration from this, we present a novel “step-by-step” assembly strategy for *in situ* growth of Co, N co-doped CNTs (Co@NCNTs) on the surface of MXenes. In this approach, Co@NCNTs could serve as spacers to prevent the accumulation of MXene nanosheets as well as function as intraparticle and interparticle charge collectors, thereby facilitating enhanced ion/electron transport channels.

Electrolytes, including potassium salt and solvent, are the bridge that connects the cathode and anode.<sup>11</sup> The electrochemical performance of batteries such as reversible capacity, lifetime, rate capability, operational voltages, and safety is closely related to the choice of electrolyte system.<sup>12</sup> The electrolyte's decomposition and solvation effects substantially impact the construction of the SEI film and the kinetics of  $\text{K}^+$  diffusion.<sup>13</sup> A robust and flexible SEI is vital for mitigating capacity degradation and minimizing irreversible side reactions.<sup>14</sup> However, there is a scarcity of reliable reports that accurately correlate electrolyte salts and solvents with the electrochemical performance of MXene-based electrodes in practical intercalation batteries (PIBs).

In this study, highly conductive elastic layers of  $\text{Ti}_3\text{C}_2\text{T}_x$  MXenes were integrated with uniformly dispersed self-grown Co, N co-doped carbon nanotubes (Co@NCNTs) through high-temperature pyrolysis of zeolitic imidazolate frameworks-67/ $\text{Ti}_3\text{C}_2\text{T}_x$ . This high-temperature pyrolysis of  $\text{Ti}_3\text{C}_2\text{T}_x$ /ZIF-67 resulted in the formation of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs. The performance of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrodes was systematically investigated using different electrolyte systems containing two potassium salts (KFSI and KPF<sub>6</sub>) in various solvents (DME and EC/DEC). The  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs composite exhibited remarkable advantages, including: (1) highly conductive nanocomposites with multiple ion-diffusion pathways, facilitating electron/ $\text{K}^+$  transport and leading to outstanding rate capability, (2) the inherent ability of  $\text{Ti}_3\text{C}_2\text{T}_x$  to accommodate strain resulting from volume changes due to its adaptive interlayer spacing, (3) strong interaction between the vertically aligned Co@NCNTs arrays and the  $\text{Ti}_3\text{C}_2\text{T}_x$  matrix, contributing to robust structural stability and efficient electron transfer, and (4) the influence of electrolyte chemistry in regulating the construction of a robust SEI layer, enabling extended cycle life and enhanced rate performance. As anticipated, the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrode demonstrated a capital reversible capacity of 260 mA h g<sup>-1</sup>, even at a demanding high current density of 500 mA g<sup>-1</sup>, after 2000 cycles in 1 M KFSI (DME) electrolyte.

## Results and discussion

### Material characterization

Fig. 1a illustrates the “step by step” process for the preparation of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs hybrids. First, the Al atomic layers of the

$\text{Ti}_3\text{AlC}_2$  MAX phase were selectively etched with hydrofluoric acid (HF) to obtain  $\text{Ti}_3\text{C}_2\text{T}_x$  with multilayered morphology. The negative charge surface termination groups, such as  $\text{OH}^-$ ,  $\text{O}^{2-}$ , and  $\text{F}^-$  on the  $\text{Ti}_3\text{C}_2\text{T}_x$  nanosheet facilitated the absorption of  $\text{Co}^{2+}$  ions through electrostatic interaction. Then, 2-methylimidazole molecules were coordinated with the surface-anchored  $\text{Co}^{2+}$  ions to construct  $\text{Ti}_3\text{C}_2\text{T}_x$ /ZIF-67 hybrids. Afterwards, the as-prepared  $\text{Ti}_3\text{C}_2\text{T}_x$ /ZIF-67 nanocomposites were pyrolyzed at 700 °C under an Ar gas atmosphere with the addition of dicyandiamide (DCDA). The 2-methylimidazole ligands were converted into N-doped carbon species, and  $\text{Co}^{2+}$  was reduced to a metallic Co phase during the high-temperature pyrolysis process. At high temperature, the Co species catalyze the transformation of N-doped carbon species into N-doped graphitic carbon nanotubes (NCNTs), leading to the successful fabrication of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs hybrids. Additionally, the presence of DCDA induces the formation of NCNTs at relatively low temperature by accelerating the graphitic structure.<sup>7b</sup>

The  $\text{Ti}_3\text{C}_2\text{T}_x$  nanosheets obtained from etching  $\text{Ti}_3\text{C}_2\text{T}_x$  with micrometer dimensions exhibit a loosely structured, accordion-like layer configuration (Fig. 1b, S1a and b†). Subjecting this accordion-like structure to ultrasonic treatment results in the exfoliation of the  $\text{Ti}_3\text{C}_2\text{T}_x$  nanosheets, which possess a smooth surface and an ultrathin thickness of 8–10 layers, with a lateral size of several micrometers (Fig. 1c and S1c†). Additionally, the interlayer spacing of the exfoliated  $\text{Ti}_3\text{C}_2\text{T}_x$  in the *c*-direction is approximately 13.6 Å, whereas the interlayer spacing of the  $\text{Ti}_3\text{C}_2\text{T}_x$  with micrometer dimensions is about 10.1 Å (Fig. 1f and g). The presence of surface termination groups facilitates the easy adsorption of  $\text{Co}^{2+}$  ions on both sides of  $\text{Ti}_3\text{C}_2\text{T}_x$  MXene through electrostatic interactions. Subsequently, the 2-methylimidazole molecules coordinate with the adsorbed  $\text{Co}^{2+}$  ions, resulting in the uniform growth and anchoring of ZIF-67 on both sides of  $\text{Ti}_3\text{C}_2\text{T}_x$  (Fig. 1d and h). The distribution of ZIF-67 nanoparticles with varying  $\text{Co}^{2+}$  concentrations is shown in Fig. S1d–l.† Following high-temperature pyrolysis, the  $\text{Co}^{2+}$  ions are reduced to a metallic Co phase, while the N-containing organic ligands transform into N-doped carbon nanotubes (Fig. 1e, i and S2†). Notably, the Co@NCNTs are evenly dispersed within the conductive layers of  $\text{Ti}_3\text{C}_2\text{T}_x$ , while the Co metal nanoparticles are confined within the NCNTs. Fig. 1i illustrates a lattice distance of 0.25 nm, which corresponds to the (0010) layer of  $\text{Ti}_3\text{C}_2\text{T}_x$ , suggesting that the  $\text{Ti}_3\text{C}_2\text{T}_x$  phase is preserved after high-temperature reduction treatment.<sup>15</sup> Furthermore, two distinct visible lattice spacings are observed, with 0.21 nm corresponding to the (222) layer of the Co metal phase and 0.34 nm corresponding to the (002) plane of graphitic carbon.<sup>16</sup> The presence of metal Co nanoparticles enhances conductivity and facilitates rapid electron transportation. Elemental mapping technology (EDX) confirms the even distribution of C, N, Co, and Ti elements in the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs hybrids (Fig. 1j). In contrast, the pyrolysis of the  $\text{Ti}_3\text{C}_2\text{T}_x$ /ZIF-67 precursor at high temperatures without the addition of DCDA leads to the formation of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NC hybrids without the production of NCNTs (Fig. S3†).

The X-ray diffraction technique was used to analyze the phase structure of  $\text{Ti}_3\text{AlC}_2$ ,  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x$ /ZIF-67, and  $\text{Ti}_3\text{C}_2\text{T}_x$ -



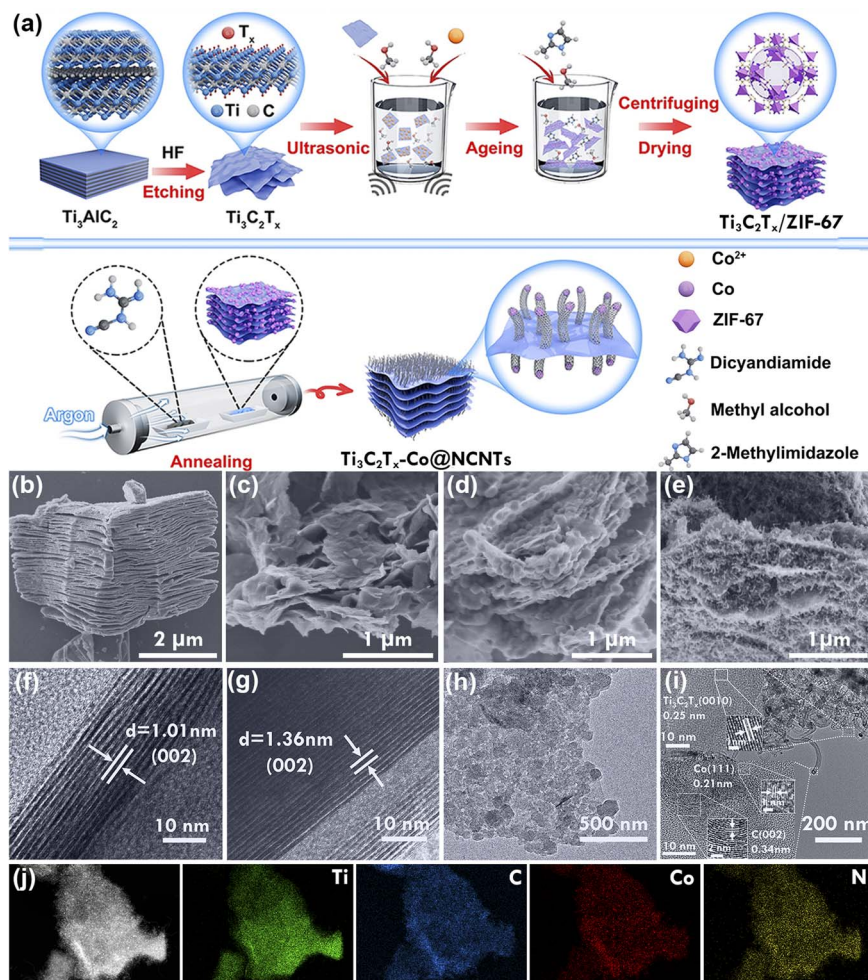


Fig. 1 (a) Scheme for the synthesis route of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ . SEM images of (b)  $\text{Ti}_3\text{C}_2\text{T}_x$ , (c) the exfoliated  $\text{Ti}_3\text{C}_2\text{T}_x$ , (d)  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$ , and (e)  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , TEM images of (f)  $\text{Ti}_3\text{C}_2\text{T}_x$ , (g)  $\text{Ti}_3\text{C}_2\text{T}_x$ , (h)  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$ , and (i)  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  and (j) elemental mapping of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ .

$\text{Co@NCNTs}$  (Fig. 2a and S4†). The disappearance of the characteristic (104) peak at  $39^\circ$  of  $\text{Ti}_3\text{AlC}_2$  confirms the removal of the Al atomic layers.<sup>17</sup> The typical (002) peak of  $\text{Ti}_3\text{C}_2\text{T}_x$  broadens and shifts from  $9.6^\circ$  to  $6.5^\circ$  after ultrasonic treatment, indicating an increase in interlayer spacing, which is consistent with HRTEM images (Fig. 1f and g).<sup>18</sup> In the  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$  hybrids, distinct peaks corresponding to ZIF-67 can be observed. The peaks at  $7.3^\circ$  and  $12.8^\circ$  are sharp and intense, indicating the presence of highly crystalline ZIF-67 particles.<sup>19</sup> After high-temperature pyrolysis, the characteristic (002) peak of  $\text{Ti}_3\text{C}_2\text{T}_x$  at  $\sim 7^\circ$  still appears in the XRD patterns, confirming the presence of the  $\text{Ti}_3\text{C}_2\text{T}_x$  phase in the hybrids. The broad peak at approximately  $26.5^\circ$  corresponds to the (002) plane of graphitized carbon. Additionally, the prominent peaks at  $44.1^\circ$  can be assigned to the metallic Co phase.<sup>20</sup>

The Raman spectra of  $\text{Ti}_3\text{C}_2\text{T}_x$  and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  show multiple similar features within the  $200\text{--}800\text{ cm}^{-1}$  range (Fig. 2b), providing further evidence of the presence of the  $\text{Ti}_3\text{C}_2\text{T}_x$  phase in the hybrids. The peak at approximately  $206\text{ cm}^{-1}$  corresponds to the  $\text{A}_{1g}$  vibration mode (out-of-plane) of C-Ti-X ( $\text{X} = \text{-F, -OH}$ ) in  $\text{Ti}_3\text{C}_2\text{T}_x$  MXenes. Additionally, the

peaks at  $363\text{ cm}^{-1}$  and  $617\text{ cm}^{-1}$  correspond to the  $\text{E}_g$  group vibrations, which include in-plane (shear) modes of C-Ti-X ( $\text{X} = \text{-F, -OH}$ ).<sup>5a</sup> The Raman peaks of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  show a noticeable shift to the right compared to pristine  $\text{Ti}_3\text{C}_2\text{T}_x$ , indicating an increase in interlayer spacing following the growth of NCNTs.<sup>21</sup> The value of  $I_D/I_G$  (the disordered carbon-induced band at  $1355\text{ cm}^{-1}$  and the graphite carbon band at  $1590\text{ cm}^{-1}$ ) is 0.92, indicating a significant number of defect sites in the nitrogen-doped carbon nanotubes. These defect sites can act as active sites for  $\text{K}^+$  storage.<sup>22</sup>

The chemical bonds at the surface were further investigated using Fourier transform infrared (FT-IR) spectroscopy (Fig. 2c). In the  $\text{Ti}_3\text{C}_2\text{T}_x$  curve, the peaks at  $3432$ ,  $1648$ ,  $1110$ , and  $652\text{ cm}^{-1}$  correspond to the  $\text{-OH}$ ,  $\text{C=O}$ ,  $\text{C-F}$ , and  $\text{Ti-C}$  stretching modes, respectively. In the  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$  hybrid, the peaks at  $683\text{ cm}^{-1}$  and  $743\text{ cm}^{-1}$  are characteristic of the out-of-plane bending of the imidazole ring. The peaks corresponding to the in-plane bending of the imidazole ring are in the range of  $900\text{--}1500\text{ cm}^{-1}$ . The characteristic peaks at  $1629\text{ cm}^{-1}$  and  $3429\text{ cm}^{-1}$  in  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  are assigned to the  $\text{C=O}$  and  $\text{-OH}$  bonds, respectively.<sup>23</sup>





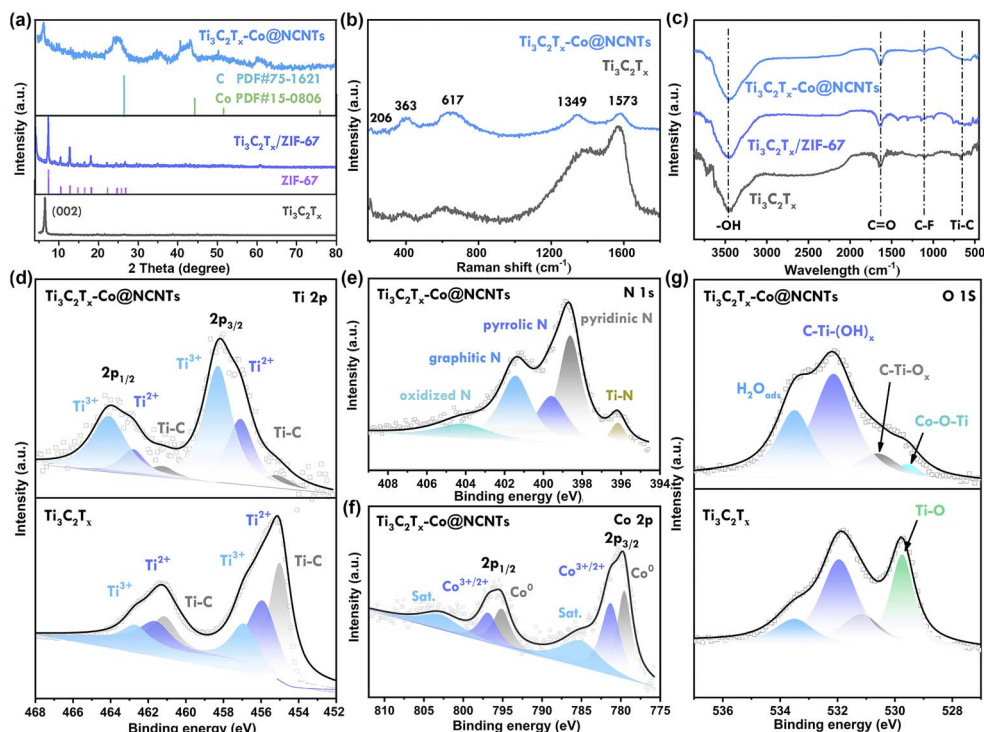


Fig. 2 (a) XRD patterns of  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$ , and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , (b) Raman spectrum of  $\text{Ti}_3\text{C}_2\text{T}_x$  and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , (c) FT-IR spectrum of  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$  and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , and high-resolution XPS spectra of (d) Ti 2p, (e) N 1s, (f) Co 2p, and (g) O 1s.

The X-ray photoelectron spectroscopy (XPS) surveys of  $\text{Ti}_3\text{C}_2\text{T}_x$  and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  are presented in Fig. S5.† In the spectra of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , the peak corresponding to the F element disappears after undergoing high-temperature strong reduction processes (Fig. S6†). The presence of surface -F groups with high concentrations hinders the excellent electrical conductivity properties of  $\text{Ti}_3\text{C}_2\text{T}_x$  MXenes;<sup>24</sup> thus the high-temperature reduction process promotes the restoration of the MXenes' intrinsic electrical conductivity. In the Ti 2p spectrum, the three dominant peaks at 461.3 eV, 462.7 eV, and 464.2 eV are associated with Ti-C,  $\text{Ti}^{2+}$ , and  $\text{Ti}^{3+}$  in the  $2p_{1/2}$  state, while the peaks at 454.9 eV, 457.1 eV, and 458.3 eV correspond to Ti-C,  $\text{Ti}^{2+}$ , and  $\text{Ti}^{3+}$  in the  $2p_{3/2}$  state, respectively (Fig. 2d).<sup>25</sup> The intensity of these peaks in the spectra of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  follows an opposite trend compared to  $\text{Ti}_3\text{C}_2\text{T}_x$ , indicating that the surface of  $\text{Ti}_3\text{C}_2\text{T}_x$  is covered by oxygen functional groups (-OH and -O-) following the high-temperature reduction treatment.<sup>26</sup> In the O 1s XPS region of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , four peaks can be fitted at 529.4, 530.7, 532.1, and 533.5 eV, respectively (Fig. 2g). Interestingly, for  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , the peak at 529.6 eV can be attributed to Ti-O-Co bonds, confirming the strong interaction between Co metal nanoparticles and  $\text{Ti}_3\text{C}_2\text{T}_x$  MXenes.<sup>27a</sup> For pure  $\text{Ti}_3\text{C}_2\text{T}_x$ , the peak at 529.6 eV can be attributed to Ti-O bonds owing to the surface oxidation.<sup>27b</sup> The peak at 530.6 eV corresponds to C-Ti-O<sub>x</sub> bonds, while the peak at 532.1 eV is assigned to C-Ti-(OH)<sub>x</sub>.<sup>28</sup> The N 1s spectrum can be fitted into five peaks at 396.1 eV (Ti-N), 398.5 eV (pyridinic N), 399.2 eV (pyrrolic N), 401.2 eV (graphitic N), and 404.5 eV (oxidized N), respectively


(Fig. 2e). Notably, pyrrolic-N and pyridinic-N contribute to the formation of defects and active sites, which can enhance potassium ion storage performance. Regarding the Co 2p spectrum, the peaks at approximately 780.5 eV, 786.4 eV, 795.9 eV, and 802.5 eV are attributed to metal Co, Co-O/Co-C-N, Co-N bonds, and the satellite peak of Co, respectively (Fig. 2f), indicating the presence of the Co metallic phase.<sup>4a,29</sup>

### Electrochemical performance for PIBs

The electrochemical performance of pure  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NC}$  was compared as anode materials in PIBs using CR2032 coin-type cells with K foil as the counter electrode. The purpose of the comparison was to demonstrate the unique microstructure of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ . Fig. 3a illustrates the cycling performance of the three samples at 100 mA g<sup>-1</sup> in 1 M KFSI (DME) electrolyte. After 80 cycles,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  exhibited a high reversible specific capacity of 360 mA h g<sup>-1</sup>, surpassing that of neat  $\text{Ti}_3\text{C}_2\text{T}_x$  (110 mA h g<sup>-1</sup>) and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NC}$  (117 mA h g<sup>-1</sup>).

The rate performance of the prepared electrodes in 1 M KFSI (DME) was evaluated and is shown in Fig. 3b. Notably, a high specific capacity of 220 mA h g<sup>-1</sup> was achieved even at a current density of 5.0 A g<sup>-1</sup>. Furthermore, the specific discharge capacity immediately recovered to 460 mA h g<sup>-1</sup> once the current density was reduced to 0.1 A g<sup>-1</sup>, suggesting that  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  exhibited strong tolerance for rapid K<sup>+</sup> uptake/release in 1 M KFSI (DME) electrolyte. The superior rate performance of the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode was further



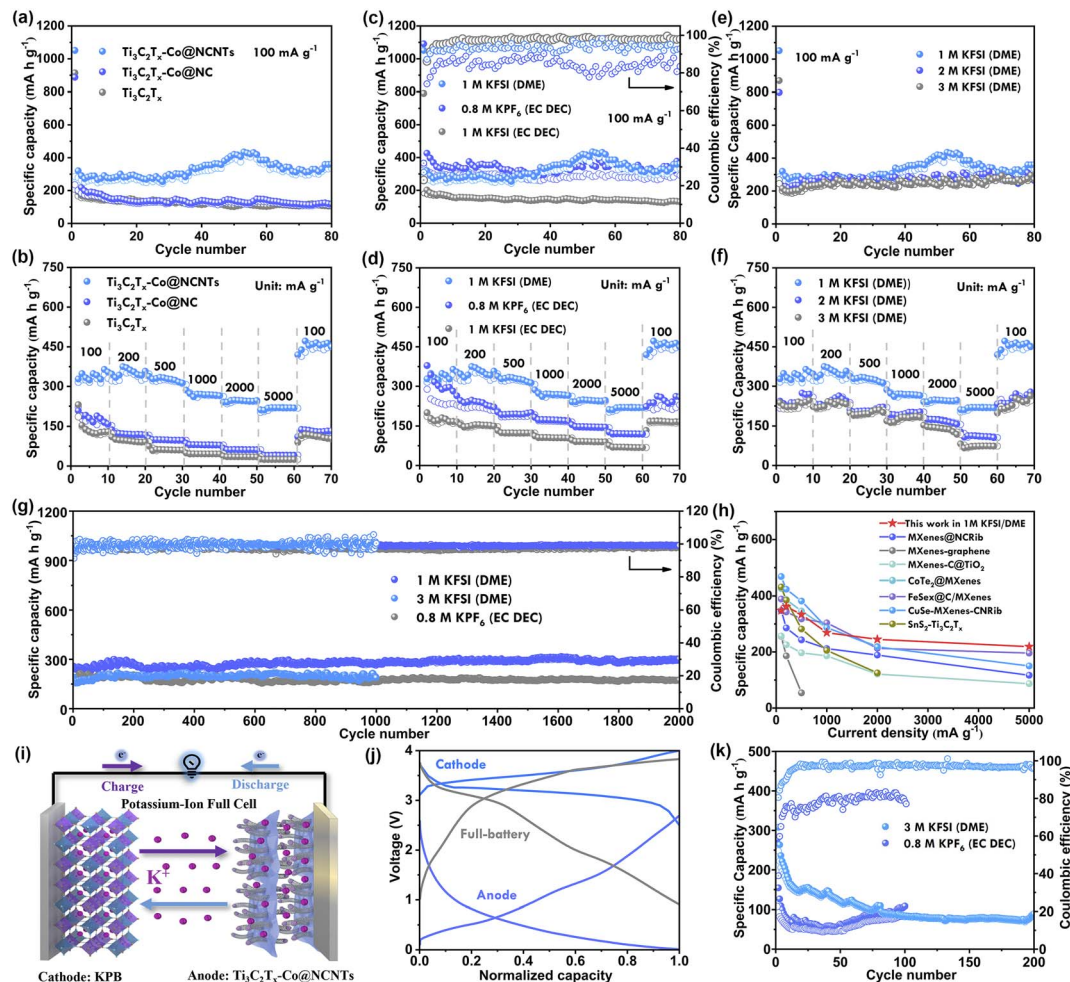

**Fig. 3** (a) Cycling performance at  $100 \text{ mA g}^{-1}$  and (b) rate performance from 100 to  $5000 \text{ mA g}^{-1}$  of the as-prepared  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NC}$  and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode in 1 M KFSI (DME). (c) Cycling performance at  $100 \text{ mA g}^{-1}$  and (d) rate performance of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  in the electrolyte of 1 M KFSI (DME), 0.8 M  $\text{KPF}_6$  (EC/DEC) and 1 M KFSI (EC/DEC). (e) Cycling and (f) rate performance of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  in KFSI (DME) with different concentrations. (g) Long-term cycling stability at  $500 \text{ mA g}^{-1}$ . (h) Comparison of the present work and recently reported literature. (i) Schematic illustration of  $\text{KPB}||\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  full cell configuration. (j) The GCD curves for the cathode, anode and full-battery, and (k) the cycling performance of the full cell at  $100 \text{ mA g}^{-1}$  in 3 M KFSI (DME) and 0.8 M  $\text{KPF}_6$  (EC/DEC). The hollow spheres in the figures represent the charge capacity and the coulombic efficiency.

supported by the charge/discharge curves at different current densities (Fig. S7†).

In contrast,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NC}$  exhibited reversible specific capacities of 183, 123, 99, 80, 62, and  $40 \text{ mA h g}^{-1}$  at various current densities, while  $\text{Ti}_3\text{C}_2\text{T}_x$  showed reversible specific capacities of 125, 97, 63, 46, 35, and  $24 \text{ mA h g}^{-1}$ . The unique architecture of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ , with  $\text{Co@NCNT}$  arrays vertically grafted between  $\text{Ti}_3\text{C}_2\text{T}_x$  MXene nanosheets, served as a conductive network to enable high electronic conductivity and multiple  $\text{K}^+$ /electrolyte transfer pathways. This distinctive feature allowed for a short electron/ $\text{K}^+$  transfer path through the conductive bridge arrays, resulting in superior rate performance.

Electrolyte systems consisting of two potassium salts (KFSI and  $\text{KPF}_6$ ) in two different solvents (DME and EC/DEC) were systematically studied for  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrodes (Fig. 3c). The initial discharge capacity in 1 M KFSI (DME) was

$1051 \text{ mA h g}^{-1}$  with an initial coulombic efficiency (CE) of 37%. After 80 cycles,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  achieved a high reversible specific capacity of  $360 \text{ mA h g}^{-1}$ . In 0.8 M  $\text{KPF}_6$  (EC/DEC), the discharge capacity was  $371 \text{ mA h g}^{-1}$  after 80 cycles. However, in 0.8 M  $\text{KPF}_6$  (EC/DEC), it exhibited poor coulombic efficiency within the first 80 cycles. In 1 M KFSI (EC/DEC), the specific discharge capacity was  $128 \text{ mA h g}^{-1}$  after 80 cycles. The specific capacities in EC/DEC solvent were much lower than those in DME solvent. The CE value was nearly 100% in 1 M KFSI (EC/DEC) during the cycling tests.

The rate performance of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  in different electrolyte systems is illustrated in Fig. 3d. The 1 M KFSI (DME) electrolyte system demonstrated the most outstanding rate performance. However, in 0.8 M  $\text{KPF}_6$  (EC/DEC), it displayed poor coulombic efficiency initially. It delivered reversible capacities of 302, 242, 194, 173, 147 and  $121 \text{ mA h g}^{-1}$  at 100, 200, 500, 1000, 2000 and  $5000 \text{ mA g}^{-1}$ , respectively. The

discharge capacity quickly recovered to  $252 \text{ mA h g}^{-1}$  once the current density was reduced to  $100 \text{ mA g}^{-1}$ . The  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  anode in 1 M KFSI (EC/DEC) displayed poor but stable reversible capacities at different current densities. Fig. S8–S10† in the manuscript display the electrochemical performance of  $\text{Ti}_3\text{C}_2\text{T}_x$ ,  $\text{Ti}_3\text{C}_2\text{T}_x/\text{ZIF-67}$ , and  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  in different electrolyte systems.

Fig. 3e and f illustrate the electrochemical performance of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  in KFSI (DME) electrolyte with different concentrations. It can be observed that there is no significant change in cycling capacity at  $100 \text{ mA g}^{-1}$  as the electrolyte concentration increases. However, a higher concentration of the electrolyte leads to increased viscosity and lower ionic conductivity, resulting in poor rate performance. The reversible specific capacities at different current densities ( $1000$ ,  $2000$ , and  $5000 \text{ mA g}^{-1}$ ) in 2 M KFSI (DME) and 3 M KFSI (DME) are as follows:  $197$ ,  $175$ , and  $110$  and  $169$ ,  $145$ , and  $73 \text{ mA h g}^{-1}$ , respectively. In comparison, the reversible specific capacities in 1 M KFSI (DME) are higher, with values of  $268$ ,  $245$ , and  $220 \text{ mA h g}^{-1}$  at  $1000$ ,  $2000$ , and  $5000 \text{ mA g}^{-1}$ , respectively.

Moreover, the long-term cyclability of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  was assessed in different electrolyte systems (Fig. 3g). In 1 M KFSI (DME) electrolyte,  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  exhibited a stable reversible capacity of approximately  $260 \text{ mA h g}^{-1}$  at  $500 \text{ mA g}^{-1}$  for up to 2000 cycles. The average capacity fading was only  $0.0053$  per cycle, demonstrating the superiority of the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  anode. In 0.8 M  $\text{KPF}_6$  (EC/DEC) electrolyte, the long-term cycling capacity retention was  $90\%$ , retaining a reversible specific capacity of  $180 \text{ mA h g}^{-1}$  at  $500 \text{ mA g}^{-1}$  after 2000 cycles. In 3 M KFSI (DME), the reversible capacity maintains  $190 \text{ mA h g}^{-1}$  at  $500 \text{ mA g}^{-1}$  after 1000 cycles, which is lower than that in 1 M KFSI (DME). Comparatively, the potassium storage performance of the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode was found to be preferable in comparison to most previously reported MXene-based materials (Fig. 3h).<sup>4a,5a,30</sup> Optimization of the electrolyte system revealed that the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  anode exhibited superior cycling stability and rate performance when paired with a 1 M KFSI (DME) electrolyte.

The unique architecture of the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode demonstrates superior potassium-storage performance in half-battery setups, encouraging further investigation of its practicability in full-batteries. To construct a full-battery setup, potassium Prussian blue (KPB) was selected as the cathode and the pre-treated  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  was used as the anode. Fig. 3j and S11† depict the typical galvanostatic charge/discharge (GCD) curves for  $\text{K}_{0.72}\text{Fe}[\text{Fe}(\text{CN})_6]$  at a current density of  $0.5 \text{ A g}^{-1}$ . The voltage window for the assembled full cell was tested between  $0.9 \text{ V}$  and  $4.0 \text{ V}$ . At a concentration of 1 M KFSI (DME), the full cell demonstrates peak charge/discharge capacity, achieving coulombic efficiency (CE) values of  $92\%$ ; however, it maintains this performance for only 62 cycles. With 3 M KFSI (DME), the cell's charge/discharge capacity stabilizes around  $100 \text{ mA h g}^{-1}$  following 200 cycles, with near-complete CE values of approximately  $100\%$ . At 0.8 M  $\text{KPF}_6$  (EC/DEC), the cell exhibits a charge/discharge capacity below  $100 \text{ mA h g}^{-1}$  and a relatively low CE of  $80\%$ . Utilizing 3 M KFSI (EC/DEC), the full cell maintains a specific capacity of

$190 \text{ mA h g}^{-1}$  over 128 cycles (as shown in Fig. 3k and S12†). Consequently, a high-concentration KFSI electrolyte system appears more suitable for the  $\text{KPB}||\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  full cell.

### Electrochemical reaction mechanism

The electrochemical reaction behaviors of  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@CNTs}$  anodes in different electrolyte systems were investigated using cyclic voltammetry (CV) tests at a scanning rate of  $0.1 \text{ mV s}^{-1}$  (Fig. 4a). In 1 M KFSI (DME) electrolyte, cathodic peaks appeared at  $0.9\text{--}1.5 \text{ V}$  in the first cycle, but disappeared in subsequent cycles, possibly due to the reductive decomposition of the electrolyte system. However, when EC and DEC were used as solvents, specifically in 0.8 M  $\text{KPF}_6$  (EC/DEC) and 1 M KFSI (EC/DEC) systems, cathodic peaks were observed at  $1.57 \text{ V}$  and  $0.68 \text{ V}$ , respectively, indicating the decomposition of EC/DEC. The redox peaks for the DME electrolyte were at lower voltages compared to the EC/DEC electrolyte, indicating different decomposition behaviors of the electrolytes. These peaks corresponded to the first voltage platform in the charge-discharge curve (Fig. S13†). Subsequent cycles showed overlapping curves, indicating high reversibility. Furthermore, the curve shapes of the subsequent cycles in the three electrolytes were similar, except for the first cycle. During the cathodic scanning, the insertion of  $\text{K}^+$  occurred within the voltage range of  $0.68\text{--}0.01 \text{ V}$ , while the anodic scanning exhibited a peak ranging from  $0.4 \text{ V}$  to  $0.6 \text{ V}$ , which indicated the process of  $\text{K}^+$  extraction from  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$ .<sup>10a</sup>

In order to gain a comprehensive understanding of the  $\text{K}^+$  storage kinetics in the fabricated electrode, the ratio of redox pseudo-capacitance is calculated through cyclic voltammetry (CV) measurements at scanning rates ranging from  $0.2$  to  $1.0 \text{ mV s}^{-1}$  (Fig. S14†). Moreover, the kinetic behavior can be inferred by examining the current-voltage ( $i$ - $v$ ) relationship described by eqn (1) and (2).

$$i = av^b \quad (1)$$

$$\log i = b \log v + \log a \quad (2)$$

The value of parameter  $b$  can be determined through analysis of the cyclic voltammetry (CV) curves. A value of  $0.5$  for  $b$  signifies a diffusion-controlled process for potassium storage, while a value of  $1$  indicates a surface-controlled process or pseudocapacitive storage. In the electrolyte systems of 1 M KFSI (DME), 0.8 M  $\text{KPF}_6$  (EC/DEC), and 1 M KFSI (EC/DEC), the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode exhibits  $b$  values of  $0.80$ ,  $0.70$ , and  $0.72$ , respectively (Fig. S14 d–f†). These results suggest that the stable storage of potassium ions in the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode is influenced by both surface-controlled capacitive storage and diffusion-controlled processes.

The eqn (3):<sup>30a</sup>

$$i = k_1v + k_2v^{1/2} \quad (3)$$

can be utilized to quantify the contribution ratio of reaction-controlled mechanisms at various scanning rates. In this equation, the constants  $k_1$  and  $k_2$  are attributed to the pseudo-





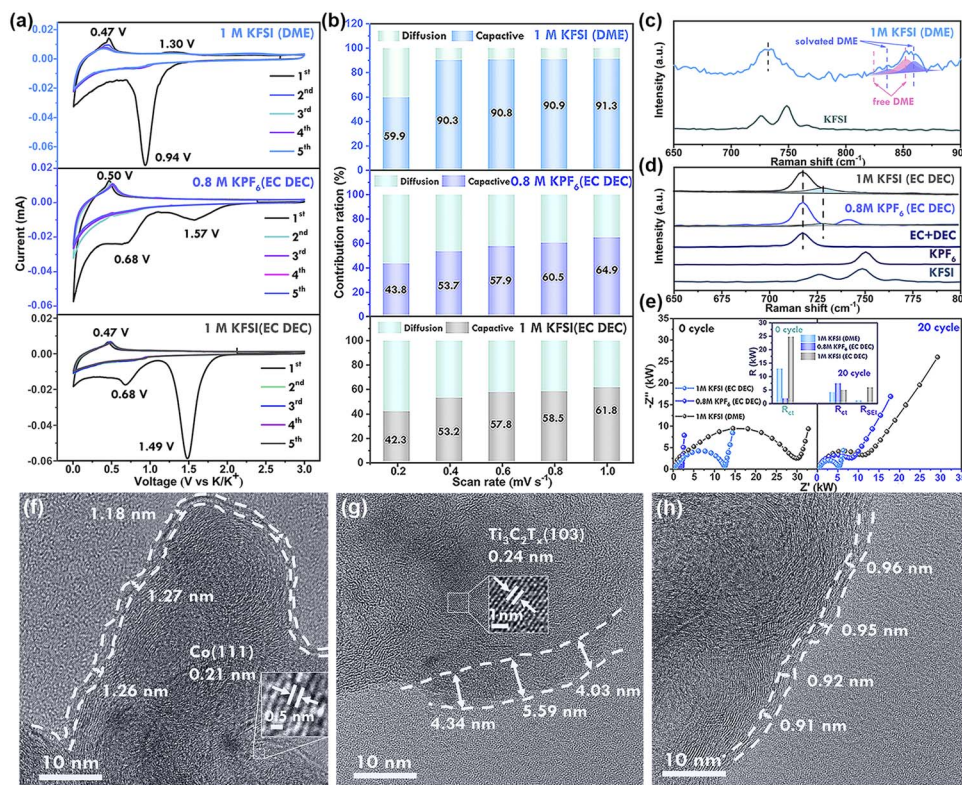


Fig. 4 (a) Cyclic voltammograms of  $\text{Ti}_3\text{C}_2\text{T}_x$  at  $0.1 \text{ mV s}^{-1}$  in different electrolyte systems. (b) Capacitive charge storage performances of  $\text{Ti}_3\text{C}_2\text{T}_x$  at different scan rates in 1 M KFSI (DME), 0.8 M  $\text{KPF}_6$  (EC/DEC) and 1 M KFSI (EC/DEC). (c) Raman spectra of KFSI-DME electrolytes. (d) Raman spectra of electrolyte systems (KFSI and  $\text{KPF}_6$  in EC/DEC). (e) EIS data in different electrolytes and modeling results of  $R_{\text{SEI}}$  and  $R_{\text{ct}}$  for 0 cycles and 20 cycles in different electrolyte systems. SEI layer on the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrode in (f) 1 M KFSI(DME), (g) 0.8 M  $\text{KPF}_6$  (EC DEC) and (h) 1 M KFSI (EC DEC).

capacitive effect and the diffusion-controlled behavior, respectively.

In the context of our study, the contribution ratios of the pseudo-capacitive effect increase gradually as the scanning rate is enhanced for the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrode in different electrolyte systems (Fig. 4b). Specifically, in the 1 M KFSI (DME) electrolyte, the calculated contribution ratios are 59.9%, 90.3%, 90.8%, 90.9%, and 91.3% for varying scan rates, highlighting the dominance of the pseudocapacitive effect in this electrolyte system. A substantial presence of pseudo-capacitance significantly accelerates reaction kinetics, consequently leading to improved rate performance (as observed in Fig. 3d). The relatively large ionic radius of potassium hinders diffusion kinetics within the crystals, consequently emphasizing the effectiveness of surface-controlled capacitive storage in achieving superior electrochemical performance, particularly at high current densities.<sup>31</sup>

Galvanostatic intermittent titration technique (GITT) tests were conducted to investigate the kinetic characteristics of the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrode prepared (Fig. S15†). The GITT profiles obtained demonstrate a consistent decline in over-potential, indicating a reliable  $\text{K}^+$  insertion process during each relaxation step. The diffusion coefficient of  $\text{K}^+$  ( $D_{\text{K}}$ ) can be calculated using eqn (4).<sup>20</sup>

$$D_{\text{K}^+} = \frac{4}{\pi} \left( \frac{m_{\text{B}} V_{\text{M}}}{M_{\text{B}} A} \right)^2 \left( \frac{\Delta E_{\text{s}}}{\tau (\text{d}E_{\text{t}}/\text{d}\sqrt{\tau})} \right)^2 \left( \tau \ll \frac{L^2}{D_{\text{K}^+}} \right) \quad (4)$$

In the 1 M KFSI (DME) electrolyte, the diffusion coefficient ranges from  $4 \times 10^{-10} \text{ cm}^2 \text{ s}^{-1}$  to  $1 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$  during discharge and from  $2 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$  to  $9 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$  during charge. In the EC/DEC solvent with a 0.8 M  $\text{KPF}_6$  (EC DEC) electrolyte, the diffusion coefficient ranges from  $2 \times 10^{-7} \text{ cm}^2 \text{ s}^{-1}$  to  $8 \times 10^{-9} \text{ cm}^2 \text{ s}^{-1}$  during discharge and from  $1 \times 10^{-7} \text{ cm}^2 \text{ s}^{-1}$  to  $1 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$  during charge. Alternatively, in the 1 M KFSI (EC DEC) electrolyte, the diffusion coefficient ranges from  $1 \times 10^{-9} \text{ cm}^2 \text{ s}^{-1}$  to  $3 \times 10^{-10} \text{ cm}^2 \text{ s}^{-1}$  during discharge and from  $1 \times 10^{-9} \text{ cm}^2 \text{ s}^{-1}$  to  $9 \times 10^{-9} \text{ cm}^2 \text{ s}^{-1}$  during charge (Fig. S15†).

The  $D_{\text{K}}$  coefficients calculated for the  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs electrode demonstrate faster kinetic behavior compared to most other MXene-based hybrids, falling within the range of  $10^{-7}$ – $10^{-10} \text{ cm}^2 \text{ s}^{-1}$ . However, it is evident that the  $D_{\text{K}}$  values decrease over longer diffusion pathways. This can be attributed to the repulsive force exerted by the previously adsorbed  $\text{K}^+$  ions at the surface sites, which hinders further insertion. Consequently, the excellent K-ion storage capacity of  $\text{Ti}_3\text{C}_2\text{T}_x$ -Co@NCNTs is not fully utilized throughout the entire charge/discharge process. Furthermore, it is important to note that



the calculated  $D_K$  value is influenced by the type of electrolyte. Specifically, for the potassium salt KFSI, the diffusion coefficient in DME (dimethyl ether) is larger than that in the EC/DEC solvent. This difference can be attributed to the size of solvated  $K^+$  ions and the viscosity of the solvent. Ester-based electrolytes typically have higher viscosity and lower diffusivity due to the strong polarization and high dielectric constant of EC molecules. Moreover, the size of  $K^+$ -DME ions is smaller than that of  $K^+$ -EC/DEC, leading to faster  $K^+$  diffusion in DME compared to that in EC/DEC. Additionally, it has been demonstrated that the diffusion coefficient is influenced by the choice of potassium salts.<sup>32</sup>

To clarify the potassium storage and diffusion features, as well as the interaction between NCNTs and  $Ti_3C_2T_x$ , further density functional theory (DFT) calculations were conducted. Fig. 5a–c illustrate the adsorption energy of  $K^+$  on the surfaces of NCNTs,  $Ti_3C_2T_x$ , and  $Ti_3C_2T_x$ -Co@NCNTs.

The adsorption sites on carbon nanotubes include the upper end of the carbon atom, the C–C bridge, and the vacancy point, with adsorption energies of  $-0.773$  eV,  $-0.881$  eV, and  $-1.141$  eV, respectively. The results indicate that  $K^+$  is more likely to diffuse at the vacancy point. On the surface of  $Ti_3C_2T_x$ , there are three adsorption sites: the upper end of the carbon atom, the upper end of the Ti atom, and the vacancy point, with adsorption energies of  $-0.631$  eV,  $-0.349$  eV, and  $-0.326$  eV, respectively. The findings suggest that  $K^+$  is more likely to diffuse at the upper end of the carbon atom of  $Ti_3C_2T_x$ . In the case of  $Ti_3C_2T_x$ -Co@NCNTs, two scenarios can be considered: the carbon skeleton region and the nitrogen-doped carbon skeleton region. When  $K^+$  diffuses in the carbon skeleton region, there are three adsorption sites: the upper end of the carbon atom, the C–C bridge, and the vacancy point, with

adsorption energies of  $-0.395$  eV,  $-0.819$  eV, and  $-0.944$  eV, respectively. When  $K^+$  diffuses in the nitrogen-doped carbon skeleton region, there are three adsorption positions: the upper end of the nitrogen atom, the vacancy point, and the N–N bridge, with adsorption energies of  $-0.940$  eV,  $-0.972$  eV, and  $-0.931$  eV, respectively. The vacancy point in the nitrogen-doped carbon skeleton region allows for easier  $K^+$  diffusion. Fig. 5d illustrates the  $K^+$  migration paths in the  $Ti_3C_2T_x$ -Co@NCNTs electrode, showing that the diffusion energy barrier for  $K^+$  is higher on the surface of carbon nanotubes and lower on  $Ti_3C_2T_x$ -Co@NCNTs compared to the surface of carbon nanotubes. The  $Ti_3C_2T_x$  MXenes, serving as the conductive matrix, not only enhance overall conductivity but also facilitate the diffusion and migration of  $K^+$ -ions (Fig. 5e). Fig. 5f provides the charge density analysis of the  $Ti_3C_2T_x$ , NCNTs, and  $Ti_3C_2T_x$ -Co@NCNTs heterostructures. The yellow cloud represents the electron-rich region, while the blue cloud represents the electron-deficient region. The differences observed demonstrate substantial charge depletions near the surface-adsorbed potassium-ion due to significant charge transfer from potassium atoms to the  $Ti_3C_2T_x$ -Co@NCNTs heterostructures. Notably, the inclusion of N and Co elements significantly enhances the charge transfer, confirming the superiority of the hybrid structure. Thus, both the experimental results and theoretical calculations confirm that the design of such a heterostructure can expedite charge/ $K^+$  transport in the battery.<sup>30c</sup>

### The electrolyte degradation (SEI formation) mechanism

The interaction between electrolyte salts and solvents in the electrolyte was investigated using Raman spectroscopy. A peak at  $718\text{ cm}^{-1}$  in the EC + DEC solvents corresponds to the C=O bending vibration mode. Upon the addition of potassium salt, a new peak emerges at  $729\text{ cm}^{-1}$ , which can be attributed to  $K^+$ -solvated EC (Fig. 4d). The proportion and intensity of the peak at  $729\text{ cm}^{-1}$  are higher in the KFSI (EC DEC) electrolyte system compared to the KPF<sub>6</sub> (EC DEC) electrolyte, indicating stronger solvation with KFSI.<sup>33</sup> This strong solvation effect reduces the number of free solvent molecules in the electrolyte system, mitigating parasitic reactions between solvent molecules and  $K^+$  metal, leading to higher CE values. In the case of KFSI, the peaks at  $725$  and  $750\text{ cm}^{-1}$  correspond to the S=O stretching vibration mode in FSI<sup>−</sup>.<sup>34</sup> These peaks merge into one peak at a higher wavenumber compared to solid KFSI, indicating fewer free FSI<sup>−</sup> anions and a stronger interaction between solvated  $K^+$  and FSI<sup>−</sup>. Upon the addition of KFSI to DME solvent, new peaks at  $835$ – $860\text{ cm}^{-1}$  appear for  $K^+$ -solvated DME. These peaks can be distinguished between  $K^+$ -solvated DME and free DME molecules. The ratio and intensity of the peaks corresponding to  $K^+$ -solvated molecules in KFSI-based electrolytes are larger than those in KPF<sub>6</sub>-based electrolytes, demonstrating a stronger solvation effect of KFSI.<sup>35</sup>

High-resolution transmission electron microscopy (HRTEM) was conducted to investigate the thickness of the solid electrolyte interphase (SEI) film in different electrolytes. The SEI film displayed an average thickness of approximately  $1.3\text{ nm}$  in  $1\text{ M}$  KFSI (DME),  $4$ – $6\text{ nm}$  in  $0.8\text{ M}$  KPF<sub>6</sub> (EC DEC), and about

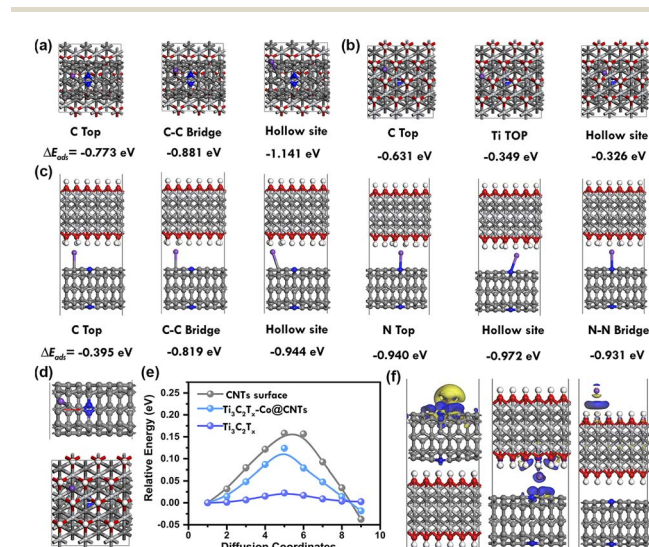


Fig. 5 Theoretical simulations of potassium adsorption/diffusion on the heterointerface between NCNTs and  $Ti_3C_2T_x$ . Potassium adsorption on the surface of (a) NCNTs, (b)  $Ti_3C_2T_x$ , and (c)  $Ti_3C_2T_x$ -Co@NCNTs, (d) potassium diffusion paths on the  $Ti_3C_2T_x$ -Co@NCNTs, (e) the corresponding diffusion barrier energy, and (f) the electron density differences.





0.9 nm in 1 M KFSI (EC DEC) (Fig. 4f–h, S16, S17, and S18<sup>†</sup>). In the case of 1 M KFSI (DME) electrolyte, the SEI layer uniformly covered the particles of the electrolyte material, maintaining its integrity. The thicker SEI film derived from the 0.8 M KPF<sub>6</sub> (EC DEC) electrolyte resulted in low initial coulombic efficiency (CE) values. Moreover, the increased thickness of the SEI layer effectively countered volume expansion during the charge/discharge process, thereby hindering anode deactivation and severe capacity decay, consequently leading to stable long-term cycling performance.<sup>36</sup>

EIS measurements were conducted to evaluate the influence of electrolytes on the internal resistance and formation of the solid electrolyte interphase (SEI) on the Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub>-Co@NCNTs anode (Fig. 4e). The resistances, including charge-transfer resistance ( $R_{ct}$ ), SEI resistance ( $R_{SEI}$ ), and internal resistance ( $R_s$ ), were determined using the equivalent circuit model depicted in Fig. S19<sup>†</sup> (ref. 37). Notably, the key distinctions among the different electrolytes lie in  $R_{SEI}$  and  $R_{ct}$ , while  $R_s$  only accounts for a minor portion of the overall resistance ( $R = R_s + R_{SEI} + R_{ct}$ ). In a 0.8 M KPF<sub>6</sub> (EC/DEC) electrolyte, the  $R_{ct}$  value significantly increased from 2 kΩ to 8 kΩ, indicating that the formation of the SEI layer hinders the diffusion of K<sup>+</sup>. Conversely, the  $R_{ct}$  values in the KFSI-based electrolyte decreased after the SEI films were formed. This suggests that the SEI film induced by the decomposition of KFSI effectively enhances the charge transport kinetics, facilitating the diffusion of potassium ions through the SEI layer to the electrode material.<sup>38</sup> Additionally, the  $R_{ct}$  value in the DME electrolyte system was lower compared to that in the EC DEC solvent, indicating faster K<sup>+</sup> transfer in DME solvent, consistent with the GITT test (Fig. S15<sup>†</sup>). The highest  $R_{SEI}$  value was observed in the 1 M KFSI (EC/DEC) electrolyte, resulting in the lowest battery capacity.

The solid electrolyte interphase (SEI) film plays a crucial role in determining the coulombic efficiency (CE) value and long-term stability of potassium-ion batteries. Therefore, the components of the SEI film were further analyzed using the *ex situ* X-ray photoelectron spectroscopy (XPS) technique (Fig. 6 and S20<sup>†</sup>). In the C 1s spectra, all four samples exhibited peaks corresponding to C–C, C–O, K<sub>2</sub>CO<sub>3</sub>, and RCOOK. The peaks of K<sub>2</sub>CO<sub>3</sub> and RCOOK are attributed to the decomposition of carbonate species, while the C–O peak is generated by the decomposition of ether-based solvents. The decomposition of carbonate species leads to the formation of C–O and C=O species on the surface layer in EC DEC solvent.<sup>39</sup> In the O 1s spectra, the peak at 530.5 eV can be attributed to K<sub>x</sub>PO<sub>y</sub>F<sub>z</sub> or SO<sub>x</sub>F, resulting from the decomposition of K<sup>+</sup> salt (KPF<sub>6</sub> and KFSI). The peaks at 533.4 eV and 534.2 eV are assigned to RO-COOK or R–OK, derived from the decomposition of carbonate-based and ether-based solvents, respectively. The F 1s spectra reveal that the SEI components in the KPF<sub>6</sub>-based electrolyte system consist of K<sub>x</sub>PF<sub>y</sub>, K<sub>x</sub>PO<sub>y</sub>F<sub>z</sub>, and K–F.<sup>40</sup>

The species distribution of solid-electrolyte interphase (SEI) layers was quantified by calculating the integral area of each peak and the proportion of each component. In a 1 M potassium fluorosilicate (KFSI) solution in dimethoxyethane (DME), the SEI film consisted of 71% inorganic salt component (KF)

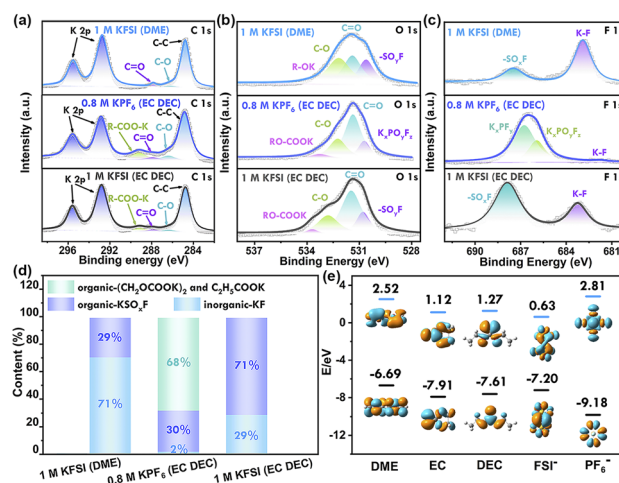


Fig. 6 XPS fitting results for the SEI layer in different electrolytes. (a) C 1s, (b) O 1s, and (c) F 1s, (d) the molecular energy levels of the HOMO and the LUMO of the solvent molecules and potassium salts: FSI<sup>+</sup> and DME in the DME electrolyte; FSI<sup>+</sup> in the EC/DEC electrolyte and KPF<sub>6</sub> in the EC/DEC electrolyte, and (e) SEI species ratio.

and 29% organic species. The inorganic salt component KF, known for its low electronic conductivity and high surface energy, facilitated the embedding and removal of K<sup>+</sup> ions and exhibited higher charge-discharge capacity compared to ester-based electrolytes. The SEI layer rich in potassium fluoride (KF) exhibited smaller charge transfer ( $R_{ct}$ ) and SEI ( $R_{SEI}$ ) resistance, as well as a larger potassium-ion diffusion coefficient, thus promoting faster reaction dynamics, as confirmed by electrochemical impedance spectroscopy (EIS). Additionally, this dense inorganic layer limited electrolyte permeability and suppressed further electrolyte decomposition, resulting in enhanced cell performance.<sup>41</sup> In a 0.8 M potassium hexafluorophosphate (KPF<sub>6</sub>) solution in ethylene carbonate (EC) and diethyl carbonate (DEC), the SEI layer primarily consisted of organic components (98%). The presence of organic components led to SEI instability and a constant process of destruction and rebuilding, resulting in low coulombic efficiency. Conversely, the SEI layer in a 1 M KFSI solution in EC/DEC consisted of both inorganic components (29% KF from the decomposition of KFSI) and organic components ((CH<sub>2</sub>-OCOOK)<sub>2</sub> and (C<sub>2</sub>H<sub>5</sub>COOK) from the decomposition of EC/DEC), leading to high coulombic efficiency nearing 100%.

The disparity in SEI layers can be elucidated by examining the LUMO energy levels of potassium salts and solvents. DFT calculations illustrate that KPF<sub>6</sub> and KPF<sub>6</sub>-solvent complexes have higher LUMO energies compared to KFSI and KFSI-solvent complexes, respectively.<sup>42</sup> This suggests that the reduction of the KFSI species is easier compared to that of KPF<sub>6</sub> (Fig. 6e). Hence, the mechanism of SEI layer formation varies in different electrolytes. In the KFSI electrolyte system, the SEI layer is mainly formed through reduction of the potassium salt, whereas in the KPF<sub>6</sub> electrolyte system, the SEI film is predominantly a result of solvent reduction. Considering the solvent effect, KFSI has a lower LUMO energy level compared to DME, but is similar to that of EC and DEC. Consequently, when



KFSI is combined with DME, electrolyte degradation primarily stems from KFSI. Conversely, in the KFSI (EC/DEC) electrolyte, there is simultaneous reduction of both EC/DEC solvent and KFSI. This explanation is consistent with the *ex situ* XPS analysis. In the KFSI (DME) electrolyte, the SEI layer is predominantly composed of KF (resulting from  $\text{FSI}^-$  decomposition), whereas in the  $\text{KPF}_6$  (EC/DEC) electrolyte, the SEI layer consists primarily of organic compounds. In contrast, the SEI layer of the KFSI (EC/DEC) electrolyte had random distribution of organic and inorganic components, which led to permeability and ongoing electrolyte decomposition, resulting in poor cyclability.<sup>12</sup> This study concludes that the formation of a KF-rich solid electrolyte interface layer on the surface of the  $\text{Ti}_3\text{C}_2\text{T}_x\text{-Co@NCNTs}$  electrode is advantageous. This can be achieved through the regulation of a KFSI-DME electrolyte system, which promotes the formation of resilient and KF-rich SEI layers.

## Conclusions

In summary, this study aimed to promote the electrochemical performance of potassium-ion storage through the construction of a hierarchical structure and the regulation of the electrolyte system. To prevent MXene aggregation and improve the conductivity of the architectures,  $\text{Co@NCNTs}$  derived from ZIF-67 were uniformly dispersed on the surface of two-dimensional layered  $\text{Ti}_3\text{C}_2\text{T}_x$ . Additionally, the relationship between electrolyte salts, solvents, and the electrochemical performance of MXene-based electrodes in PIBs was investigated. The combination of KFSI salt and DME solvent facilitated sufficient  $\text{K}^+$ -ion solvation and the formation of a high-KF SEI. This, in turn, effectively prevented SEI corrosion, greatly enhancing cycling stability and rate capability. This work provides insights into the multifunctionality of electrolytes in PIBs and proposes systematic evaluation methodologies for future electrolyte engineering.

## Data availability

All the data supporting this article have been included in the main text and the ESI.<sup>†</sup>

## Author contributions

X. X., Q. J., and C. Y. designed the experiments, participated in analysing the data, and drafted the manuscript; J. R., H. W., X. L., Z. L. and W. Z. discussed the characterization data; Y. C., C. Z., J. H., and T. Z. conceived the project and provided guidance and supervision throughout the work. All authors have approved the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (21806187, 22272207, and 52302205),

Fundamental Research Funds for the Central Universities of South-Central Minzu University (CZY23015, CZZ23008), the Anhui Provincial Natural Science Foundation for Outstanding Young Scholar (2208085Y05), the Anhui Provincial Scientific Reuter Foundation for Returned Scholars (2022LCX030), and the Excellent Research and Innovation Team Project of Anhui Province (2022AH010001).

## Notes and references

- (a) M. Shen, H. Ding, L. Fan, A. M. Rao, J. Zhou and B. Lu, *Adv. Funct. Mater.*, 2023, **33**, 2213362; (b) X. Sun, Z. Li, Z. Liu, X. Lv, K. Shi, R. Chen, F. Wu and L. Li, *Adv. Funct. Mater.*, 2023, **33**, 2300125; (c) S. Imtiaz, N. Kapuria, I. S. Amiin, A. Sankaran, S. Singh, H. Geaney, T. Kennedy and K. M. Ryan, *Adv. Funct. Mater.*, 2022, **33**, 2209566; (d) J. Chen, D. An, S. Wang, H. Wang, Y. Wang, Q. Zhu, D. Yu, M. Tang, L. Guo and H. Wang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202307122; (e) M. Tang, S. Dong, J. Wang, L. Cheng, Q. Zhu, Y. Li, X. Yang, L. Guo and H. Wang, *Nat. Commun.*, 2023, **14**, 6004.
- (a) Y. Chen, B. Xi, M. Huang, L. Shi, S. Huang, N. Guo, D. Li, Z. Ju and S. Xiong, *Adv. Mater.*, 2022, **34**, 2108621; (b) L. Wu, H. Fu, S. Li, J. Zhu, J. Zhou, A. M. Rao, L. Cha, K. Guo, S. Wen and B. Lu, *Nat. Commun.*, 2023, **14**, 644.
- Y. Wu, Y. Sun, J. Zheng, J. Rong, H. Li and L. Niu, *Chem. Eng. J.*, 2021, **404**, 126565.
- (a) X. Xu, Y. Zhang, H. Sun, J. Zhou, Z. Liu, Z. Qiu, D. Wang, C. Yang, Q. Zeng, Z. Peng and S. Guo, *Adv. Mater.*, 2021, **33**, 2100272; (b) D. Sha, C. Lu, W. He, J. Ding, H. Zhang, Z. Bao, X. Cao, J. Fan, Y. Dou, L. Pan and Z. Sun, *ACS Nano*, 2022, **16**, 2711–2720.
- (a) B. Cao, H. Liu, P. Zhang, N. Sun, B. Zheng, Y. Li, H. Du and B. Xu, *Adv. Funct. Mater.*, 2021, **31**, 2102126; (b) C. Liu, Y. Bai, W. Li, F. Yang, G. Zhang and H. Pang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202116282; (c) S. H. Yang, Y. J. Lee, H. Kang, S.-K. Park and Y. C. Kang, *Nano-Micro Lett.*, 2021, **14**, 17.
- X. Cao, Y. You, D. Sha, H. Xia, H. Wang, J. Zhang, R. Hu, Y. Wei, Z. Bao, Y. Xu, L. Pan, C. Lu, W. He, M. Zhou and Z. Sun, *Adv. Funct. Mater.*, 2023, **33**, 2303275.
- (a) L. P. Yu, X. H. Zhou, L. Lu, L. Xu and F. J. Wang, *ChemSusChem*, 2021, **14**, 5079–5111; (b) P. Su, H. Xiao, J. Zhao, Z. Shao, C. Li and Q. Yang, *Chem. Sci.*, 2013, **4**, 2941.
- K. Yang, M. Luo, D. Zhang, C. Liu, Z. Li, L. Wang, W. Chen and X. Zhou, *Chem. Eng. J.*, 2022, **427**, 132002.
- (a) X. Wang, S. Wang, J. Qin, X. Xie, R. Yang and M. Cao, *Inorg. Chem.*, 2019, **58**, 16524–16536; (b) H. Li, R. Chen, M. Ali, H. Lee and M. J. Ko, *Adv. Funct. Mater.*, 2020, **30**, 2002739; (c) Y. Yue, Y. Wang, X. Xu, C. Wang, Z. Yao and D. Liu, *Ceram. Int.*, 2022, **48**, 6338–6346; (d) W. Wang, F. Xiong, S. Zhu, J. Chen, J. Xie and Q. An, *Escience*, 2022, **2**, 278–294.
- (a) W. Zhao, X. Xu, L. Wang, Y. Liu, T. Zhou, S. Zhang, J. Hu and Q. Jiang, *J. Energy Chem.*, 2022, **75**, 55–65; (b) D. Xu, Q. Cheng, P. Saha, Y. Hu, L. Chen, H. Jiang and C. Li, *Adv. Funct. Mater.*, 2023, **33**, 2211661.



- 11 M. Zhou, P. Bai, X. Ji, J. Yang, C. Wang and Y. Xu, *Adv. Mater.*, 2021, **33**, 2003741.
- 12 Q. Li, Z. Cao, W. Wahyudi, G. Liu, G.-T. Park, L. Cavallo, T. D. Anthopoulos, L. Wang, Y.-K. Sun, H. N. Alshareef and J. Ming, *ACS Energy Lett.*, 2020, **6**, 69–78.
- 13 M. Gu, L. Fan, J. Zhou, A. M. Rao and B. Lu, *ACS Nano*, 2021, **15**, 9167–9175.
- 14 G. Ma, Y. Wang, J. Song, K. Song, N. Wang, J. Yang and Y. Qian, *Carbon Energy*, 2022, **4**, 332–345.
- 15 X. Liu, Y. Liu, S. Dong, X. Zhang, Y. Wei, L. Lv and S. He, *ACS Appl. Nano Mater.*, 2023, **6**, 9579–9587.
- 16 Z. Liang, N. Kong, C. Yang, W. Zhang, H. Zheng, H. Lin and R. Cao, *Angew. Chem., Int. Ed.*, 2021, **60**, 12759–12764.
- 17 Y. Zhu, Z. Wang, R. Zhao, Y. Zhou, L. Feng, S. Gai and P. Yang, *ACS Nano*, 2022, **16**, 3105–3118.
- 18 L. Liu, M. Orbay, S. Luo, S. Duluard, H. Shao, J. Harmel, P. Rozier, P. L. Taberna and P. Simon, *ACS Nano*, 2022, **16**, 111–118.
- 19 Y. Zhang, J. Wu, S. Zhang, N. Shang, X. Zhao, S. M. Alshehri, T. Ahamad, Y. Yamauchi, X. Xu and Y. Bando, *Nano Energy*, 2022, **97**, 107146.
- 20 L. Wang, Q. Jiang, K. Yang, Y. Sun, T. Zhou, Z. Huang, H.-J. Yang and J. Hu, *J. Colloid Interface Sci.*, 2021, **601**, 60–69.
- 21 A. Sarycheva, M. Shanmugasundaram, A. Krayev and Y. Gogotsi, *ACS Nano*, 2022, **16**, 6858–6865.
- 22 J. S. Lee, R. Saroha and J. S. Cho, *Nano-Micro Lett.*, 2022, **14**, 113.
- 23 M. Xu, L. Liang, J. Qi, T. Wu, D. Zhou and Z. Xiao, *Small*, 2021, **17**, 2007446.
- 24 Y. An, Y. Tian, Q. Man, H. Shen, C. Liu, S. Xiong and J. Feng, *Nano Lett.*, 2023, **23**, 5217.
- 25 S. Kim, H. Shin, J. Lee, C. Park, Y. Ahn, H.-J. Cho, S. Yuk, J. Kim, D. Lee and I.-D. Kim, *ACS Nano*, 2023, **17**, 19387–19397.
- 26 C. E. Park, G. H. Jeong, J. Theerthagiri, H. Lee and M. Y. Choi, *ACS Nano*, 2023, **17**, 7539–75479.
- 27 (a) L. Yao, Q. Gu and X. Yu, *ACS Nano*, 2021, **15**, 3228–3240; (b) J. Cao, Z. Sun, J. Li, Y. Zhu, Z. Yuan, Y. Zhang, D. Li, L. Wang and W. Han, *ACS Nano*, 2021, **15**, 3423–3433.
- 28 H. Huang, J. Cui, G. Liu, R. Bi and L. Zhang, *ACS Nano*, 2019, **13**, 3448–3456.
- 29 P. Liu, S. Gao, G. Zhang, Y. Huang, W. You and R. Che, *Adv. Funct. Mater.*, 2021, **31**, 2102812.
- 30 (a) J. Cao, L. Wang, D. Li, Z. Yuan, H. Xu, J. Li, R. Chen, V. Shulga, G. Shen and W. Han, *Adv. Mater.*, 2021, **33**, 2101535; (b) R. Zhang, Y. Tian, T. Otitoju, Z. Feng, Y. Wang and T. Sun, *Small*, 2023, **19**, 2302148; (c) J. Cao, Z. Sun, J. Li, Y. Zhu, Z. Yuan, Y. Zhang, D. Li, L. Wang and W. Han, *ACS Nano*, 2021, **15**, 3423–3433; (d) H. Liu, Y. He, H. Zhang, S. Wang, K. Cao, Y. Jiang, X. Liu and Q.-S. Jing, *J. Colloid Interface Sci.*, 2022, **606**, 167–176.
- 31 (a) X. Chen, S. Xia, T. Tan, Y. Zhu, L. Li, Q. Zhu and W. Zhang, *Inorg. Chem. Front.*, 2023, **10**, 4414–4424; (b) T. Lei, M. Gu, H. Fu, J. Wang, L. Wang, J. Zhou, H. Liu and B. Lu, *Chem. Sci.*, 2023, **14**, 2528; (c) P. Wang, X. Dai, P. Xu, S. Hu, X. Xiong, K. Zou, S. Guo, J. Sun, C. Zhang, Y. Liu, T. Zhou and Y. Chen, *Escience*, 2023, **3**(1), 100088; (d) X. Wu, Z. Li, J. Liu, W. Luo, J. Gaumet and L. Mai, *Rare Met.*, 2022, **41**, 3446–3455.
- 32 L. Wang, J. Yang, J. Li, T. Chen, S. Chen, Z. Wu, J. Qiu, B. Wang, P. Gao, X. Niu and H. Li, *J. Power Sources*, 2019, **409**, 24.
- 33 H. Wang, D. Yu, X. Wang, Z. Niu, M. Chen, L. Cheng, W. Zhou and L. Guo, *Angew. Chem., Int. Ed.*, 2019, **58**, 16451.
- 34 L. Li, S. Zhao, Z. Hu, S.-L. Chou and J. Chen, *Chem. Sci.*, 2021, **12**, 2345–2356.
- 35 H. J. Liang, Z. Y. Gu, X. X. Zhao, J. Z. Guo, J. L. Yang, W. H. Li, B. Li, Z. M. Liu, W. L. Li and X. L. Wu, *Angew. Chem., Int. Ed.*, 2021, **60**, 26837–26846.
- 36 Y. Liu, C. Gao, L. Dai, Q. Deng, L. Wang, J. Luo, S. Liu and N. Hu, *Small*, 2020, **16**, 2004096.
- 37 Z. Wu, J. Zou, S. Shabanian, K. Golovin and J. Liu, *Chem. Eng. J.*, 2022, **427**, 130972.
- 38 B. Li, J. Zhao, Z. Zhang, C. Zhao, P. Sun, P. Bai, J. Yang, Z. Zhou and Y. Xu, *Adv. Funct. Mater.*, 2019, **29**, 1807137.
- 39 Y. Xu, T. Ding, D. Sun, X. Ji and X. Zhou, *Adv. Funct. Mater.*, 2023, **33**, 2211290.
- 40 (a) L. Zhou, Z. Cao, J. Zhang, H. Cheng, G. Liu, G. T. Park, L. Cavallo, L. Wang, H. N. Alshareef, Y. K. Sun and J. Ming, *Adv. Mater.*, 2021, **33**, 2005993; (b) J. Zhao, C. Li, G. Chen, F. Ji, Y. Shen, J. Peng and W. Wang, *Rare Met.*, 2022, **41**, 2259–2267.
- 41 X. Du and B. Zhang, *ACS Nano*, 2021, **15**, 16851–16860.
- 42 J. Li, Y. Hu, H. Xie, J. Peng, L. Fan, J. Zhou and B. Lu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202208291.

