Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2024, 15, 17937

dll publication charges for this article have been paid for by the Royal Society of Chemistry

Received 8th May 2024 Accepted 26th September 2024

DOI: 10.1039/d4sc03029j

rsc.li/chemical-science

Crystal engineering of a new platform of hybrid ultramicroporous materials and their C_2H_2/CO_2 separation properties†

Daniel J. O'Hearn, † Debobroto Sensharma, († Asif Raza, († † * Asif Raza, († *

Hybrid ultramicroporous materials (HUMs) comprised of combinations of organic and inorganic linker ligands are a leading class of physisorbents for trace separations involving C1, C2 and C3 gases. First generation HUMs are modular in nature since they can be self-assembled from transition metal cations, ditopic linkers and inorganic "pillars", as exemplified by the prototypal variant, SIFSIX-3-Zn (3 = pyrazine, SIFSIX = SiF_6^{2-}). Conversely, HUMs that utilise chelating ligands such as ethylenediamine derivatives are yet to be explored as sorbents. Herein, we report the structures and sorption properties of two HUMs based upon the chelating ligand N^1, N^2 -bis(pyridin-4-ylmethyl)ethane-1,2-diamine (enmepy), $[Zn(enmepy)(SiF_6)]_n$ (SIFSIX-24-Zn) and $[Zn(enmepy)(SO_4)]_n$ (SOFOUR-2-Zn). These HUMs are isostructural and exhibit high C_2H_2 uptakes of 85 cm³ g⁻¹ (3.79 mmol g⁻¹) and 79 cm³ g⁻¹ (3.52 mmol q^{-1}), and C_2H_2/CO_2 IAST selectivities of 7.4 and 8.1 (1 bar, 1:1 mixture, 298 K), respectively. Dynamic column breakthrough experiments resulted in separation factors of 5.26 and 2.05, and CO2 effluent purities of 99.991 and 99.989%, respectively. Temperature programmed desorption experiments at 60 °C resulted in rapid desorption of CO₂, followed by fuel grade C₂H₂ (>98%), affording productivities of 9.45 and 7.96 L kg⁻¹ and maximum C₂H₂ outlet purities of 99.92% and 99.66%, respectively. This study introduces the use of diamine chelating ligands in HUMs for gas separations through two parent sorbents that are prototypal for families of related materials, one of which, SOFOUR-2-Zn, uses the earth-friendly sulfate anion as a pillar.

Introduction

The first studies that confirmed permanent porosity in porous coordination networks (PCNs)¹-³ spawned intense interest in study of PCNs⁴,⁵ for their potential utility for gas separations including purification of light hydrocarbons.⁶-९ One class of PCN, hybrid ultramicroporous materials (HUMs), is comprised of inorganic and organic linker ligands and can exhibit highly selective physisorption.¹⁰ Their performance can be attributed to their ultramicroporous (≤7.0 Å) nature, which results in tight sorbate binding, and the strong electrostatics of the inorganic anions that line the pores,¹¹ in effect creating a high density of

highly selective binding sites.⁵ The prototypal HUM, $[Zn(SiF_6)(pyz)_2]_n$ (SIFSIX-3-Zn), is comprised of an N-donor linker ligand, pyrazine (3), that links Zn2+ cations to form a cationic 2D square lattice topology, sql, network and SiF₆²⁻ (SIFSIX) anions that pillar the sql nets to form a 3D primitive cubic, pcu, topology network. SIFSIX-3-Zn was found to offer exceptional trace CO₂ capture properties over N₂ and CH₄, ond its inherent modularity enabled systematic fine-tuning of composition through substitution of the metal cation, organic linker ligand and/or the SIFSIX pillar, affording improvements in stability and performance. 10,13,14 Second generation HUMs pillared by SIFSIX and other MF_6^{2-} anions (M = Si, Ge, Sn, Ti, Zr) belong to the MFSIX platform. 15 Other HUM platforms have been based on different inorganic pillars, including DICRO $(Cr_2O_7^{2-})$, 16,17 FOXY $(NbOF_5^{2-})$, 18,19 MFFIVE (AlF_5^{2-}) , 20 mmo topology nets (CrO₄²⁻,MoO₄²⁻, WO₄²⁻),²¹ and, most recently, **SOFOUR** (SO₄²⁻).²²

A potential application for HUMs is acetylene (C_2H_2) purification. C_2H_2 is typically produced *via* oxidative coupling of CH_4 with CO_2 as a by-product. Since C_2H_2 and CO_2 have the same kinetic diameter of 3.3 Å and similar boiling/sublimation points of 188.4 and 194.7 K, respectively, 5.6 sorptive separation is

^aDepartment of Chemical Sciences, Bernal Institute, University of Limerick, Limerick V94 T9PX, Ireland. E-mail: matthias.vandichel@ul.ie; soumya.mukherjee@ul.ie; xtal@ul.ie

^bSSPC, Science Foundation Ireland Research Centre for Pharmaceuticals, University of Limerick, Limerick V94 T9PX, Ireland

[†] Electronic supplementary information (ESI) available: Synthesis, gas sorption, modelling details, crystallographic information. CCDC 2206134. For ESI and crystallographic data in CIF or other electronic format see DOI: https://doi.org/10.1039/d4sc03029j

[‡] These authors contributed equally to this work.

challenging. Industrially, purification is typically achieved using organic solvents, which is inefficient and requires multiple steps to reach the required levels of purity. HUMs such as SIFSIX-dps-Cu,²³ UTSA-300a ²⁴ and DICRO-4-Ni-i ²⁵ selectively adsorb C_2H_2 *via* strong C_2H_2 binding sites in which F atoms serve as hydrogen bond acceptors, particularly when spaced optimally (*ca.* 7 Å) to interact with both ends of a C_2H_2 molecule.⁶ Recently, the linker ligand bpe, 1,2-bis(4-pyridyl)ethane, afforded a layered flexible HUM, sql-SIFSIX-bpe-Zn, the activated phase of which, sql-SIFSIX-bpe-Zn-β, set a new benchmark for C_2H_2 adsorption enthalpy (Q_{st}) of 67.5 kJ mol⁻¹.²⁶ This strong binding was attributed to induced fit of C_2H_2 molecules by enzyme-like adaptable sorbent binding sites and sql-SIFSIX-bpe-Zn-β was found to be highly C_2H_2 -selective over both ethylene and CO_2 .

Although families of pillared HUMs composed of linear or angular ditopic linker ligands are the most commonly studied HUM variants, other ligand types are possible. HUMs with 4,6connected fsc topology are composed of tetratopic ligands where the ligand serves as a 4-c node and the metal ion serves as a 6-c node. Examples of ligands and their respective fsc topology HUMs are as follows: metalloligand [Cu₂(3-(pyridin-4-yl) acrylate)₄] in fsc-2-SIFSIX;²⁷ tetra-(pyridin-4-yl)porphyrin in CPM-131;²⁸ "FTPFs" Cu-Nb-M (M = Zn, Fe, Ni);²⁹ 1,2,4,5-tetra(pyridin-4yl)benzene (tepb) in ZJU-280 (SIFSIX-22-Cu),30 SIFSIX-22-Zn,22,31 SOFOUR-1-Zn,²² and TIFSIX-Cu-TPB (TIFSIX-6-Cu).³² These materials have been studied for CO2 capture,27 electrocatalysis,29 C₂H₂/C₂H₄ separation,³⁰ and C₂H₂/CO₂ separation.^{22,26} Since the ligand serves as a 4-c node, such PCNs are also amenable to pillar substitution as exemplified by replacement of the SIFSIX pillar in SIFSIX-22-Zn by SO_4^{2-} (SOFOUR) in SOFOUR-1-Zn ²² and **SOFOUR-DPDS-Ni** (4-DPDS = 4,4'-dipyridyldisulfide),³³ and the use of other fluorinated pillars, e.g. TiF₆²⁻, SnF₆²⁻, GeF₆²⁻ ZrF₆²⁻ and TaF₇²⁻, while retaining **fsc** topology.³⁴ The SO₄² pillar has also been used in HUMs such as CuSO₄(1,4-bin)_{1.5} (1,4bin = 1,4-bisimidazole naphthalene),35 and SOFOUR-TEPE-Zn (TEPE = 1,1,2,2-tetra(pyridin-4-yl) ethene).³⁶

Nevertheless, the availability of linker ligands suitable for HUMs remains somewhat limited in scope and derivatives of chelating ligands such as ethylenediamine (en), which represent a potentially inexpensive and versatile class of ligand, are to our knowledge unexplored. This is despite en and its derivatives representing 7.27% (55 046 entries) of coordination compounds archived in the Cambridge Structural Database (CSD version 5.45, September 2024).³⁷ In this contribution, we report a successful crystal engineering approach to preparing the prototypal members of two HUM platforms comprising a pyridyl functionalised chelating en ligand, enmepy, and their sorption properties in the context of C₂H₂/CO₂ gas separations.

Results and discussion

CSD analysis

In order to design and characterise new HUM platforms based on en derivatives, we first looked for reports of en chelates pillared by MF₆ anions (M = Si, Ge, Sn, Ti, Zr, Hf). Database mining of the CSD for coordination compounds containing both an en (or derivative) chelate and a coordinated MFSIX anion afforded just five hits (Table S1 and Fig. S1a \dagger): two ZrF₆²⁻ complex anions $([(ZrF_6)_2(ZrF_5(OH_2))_2]^{6-}$ and $[(ZrF_6)_2]^{4-}$; three 1D chains involving SIFSIX or TiF_6^{2-} (TIFSIX) linkers $([Cu(en)_2(SiF_6)]_n$ and $[Cu(en)_2(TiF_6)]_n$). No apparent porosity was present or studied in these compounds.^{38,39} This lack of sorption candidates prompted us to look at the earth-friendly inorganic pillar SOFOUR and our search (Fig. S1b†) resulted in 25 hits (20 distinct compounds, Table S2;† corresponding to chelating ligands listed in Fig. S2†). $[Cu(en)(OH_2)_2(SO_4)]_n$ and $[Zn(en)_2(SO_4)]_n$ are 1D chains with no apparent or permanent porosity. However, $[\mathbf{Zn(enmepy)(SO_4)}]_n$ (CSD refcode ZOM-NOG, hereinafter referred to as SOFOUR-2-Zn) is composed of the chelating **en** derivative N^1 , N^2 -bis(pyridin-4-ylmethyl)ethane-1,2-diamine (enmepy) and Zn²⁺ cations that form a sql network pillared by SOFOUR to afford a 3D pcu network. Even though SOFOUR-2-Zn contains 1D ultramicropores, no gas sorption data was reported.46 We then searched for other structures containing enmepy chelates that form sql nets similar to SOFOUR-2-Zn. This search, which used the query in Fig. S3,† afforded 62 hits, manual inspection of which revealed 31 sql nets (see Table S3†). The majority (22) are not pillared, with axial positions metal cations coordinated by terminal ligands. The remaining entries were found to be pillared by either 1,4benzenedicarboxylate derivatives, 47,48 MO₄ 2- (M = Cr, Mo) or, in the case of SOFOUR-2-Zn, SOFOUR.46 The earth friendly characteristics of **SOFOUR** over CrO₄²⁻ and MoO₄²⁻, motivated us to characterise the sorption properties of SOFOUR-2-Zn along with its new SIFSIX variant, $[Zn(enmepy)(SiF_6)]_n$ (SIFSIX-24-Zn).

Crystal structures

SOFOUR-2-Zn was previously reported in 2014, crystallising in the monoclinic space group C2.⁴⁶ Each octahedral Zn²⁺ cation is chelated by amino groups of one **enmepy** and two pyridyl groups from two different **enmepy** ligands to fill its equatorial positions (Fig. 1a), thereby generating a 2D cationic network with **sql** topology (Fig. 1b). In each axial position, a **SOFOUR** anion serves as a pillar to adjacent **sql** layers so as to form a **pcu** topology network with an intermetallic distance between **sql** layers of 6.74 Å (Fig. 1c). The **sql** layers stack such that triangular 1D channels containing hydrate molecules run parallel to the crystallographic c-axis (Fig. 1b). The calculated void space is 40.9% of unit cell volume after removal of hydrate molecules (mercury contact surface, probe radius 1.2 Å).⁴⁹

SIFSIX-24-Zn was prepared by reacting **enmepy** with ZnSiF₆. Crystals suitable for single crystal X-ray diffraction, SCXRD, were obtained by diffusion of a methanolic solution of **enmepy** layered onto an ethylene glycol solution of ZnSiF₆ (see ESI† for details). SCXRD data revealed that **SIFSIX-24-Zn** had crystallised

Open Access Article. Published on 27 September 2024. Downloaded on 11/29/2025 4:55:49 AM.

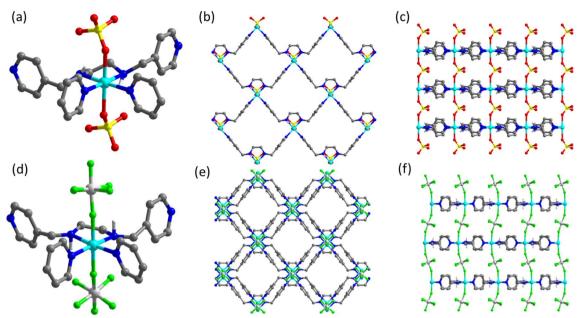


Fig. 1 Crystal structures of SIFSIX-24-Zn and SOFOUR-2-Zn (C-H atoms omitted for clarity, C = grey, H = white, N = blue, O = red, F = green, S = yellow, Si = light beige, Zn = cyan). (a) The octahedral coordination environment around Zn^{2+} in SOFOUR-2-Zn, (b) SOFOUR-2-Zn packing viewed along a-axis, (c) SOFOUR-2-Zn crystal packing viewed along c-axis, (d) the octahedral coordination environment around Zn^{2+} in SIFSIX-24-Zn. (e) SIFSIX-24-Zn crystal packing viewed along c-axis.

in the chiral orthorhombic space group $C222_1$. The equatorial environment of the Zn^{2+} cations is similar to that of **SOFOUR-2-Zn** but the **SIFSIX** pillars form shorter bonds with the Zn cation at the axial positions (Zn-F = 2.148(5) Å νs . Zn-O = 2.223 Å, Fig. 1d). **SIFSIX-24-Zn** formed the same **sql** layers found in **SOFOUR-2-Zn**, resulting in the **pcu** network illustrated in Fig. 1e and f. The larger **SIFSIX** anion resulted in intermetallic distance between layers of 7.5759(16) Å (0.833 Å longer than **SOFOUR-2-Zn**, Fig. 1f). **SIFSIX-24-Zn** possesses similar 1D pores to **SOFOUR-2-Zn** but with diffuse electron density which was accounted for by the PLATON SQUEEZE⁵⁰ procedure in the final structure refinement. The void space (Mercury contact surface, probe radius 1.2 Å) was calculated to be 37.9% of unit cell volume. Further crystallographic details are presented in Table S4.†

In both **SOFOUR-2-Zn** and **SIFSIX-24-Zn**, all **enmepy** ligands within a **sql** layer orient in the same direction, precluding a crystallographic inversion centre. The stacking of **sql** layers differs between the two compounds. In **SOFOUR-2-Zn**, each layer is identical and orients in the same direction, whereas in **SIFSIX-24-Zn**, the layers alternate in direction and chirality and a pseudo centre of symmetry is present. Though this detail may seem inconsequential for gas adsorption, it impacts pore shape as becomes apparent when examining crystal packing (Fig. 1). The chirality of the **sql** layers formed by **enmepy** has been explored by Wen *et al.*, where homochiral batches of crystals could be obtained when using a homochiral template during crystallisation.^{51–53} The **SIFSIX-24-Zn** crystal used for SCXRD study was found to be a racemic twin with a Flack parameter of 0.5 (Table S4†).^{46,47}

Gas sorption

Pure gas sorption studies. In order to perform sorption studies, bulk samples of SOFOUR-2-Zn and SIFSIX-24-Zn were prepared by mixing methanolic solutions of enmepy with aqueous solutions of ZnSO₄ and ZnSiF₆, respectively, at room temperature, to obtain microcrystalline powders (see ESI† for synthetic details) with Powder X-ray diffraction (PXRD) patterns matching those calculated from SCXRD data (Fig. S4†). Thermogravimetric analysis (TGA) of SOFOUR-2-Zn and SIFSIX-24-Zn indicated loss of solvent molecules at 90 and 75 °C, respectively, and thermal stability up to approximately 300 °C and 200 °C, respectively (Fig. S5†). Following activation at 60 °C under dynamic vacuum, both materials exhibited type-I isotherms for CO2 at 195 K, with saturation uptakes of 135 cm 3 g $^{-1}$ and 178 cm 3 g $^{-1}$, respectively (Fig. 2a), and apparent BET surface areas of 452 m² g⁻¹ and 590 m² g⁻¹, respectively (Fig. S6 and S7†). The Horvath-Kawazoe differential pore volume plots from 195 K CO2 isotherms for both compounds were centred around 5.0 Å, classifying them as ultramicroporous (Fig. S8†). SIFSIX-24-Zn exhibited a minor inflection in the 195 K CO₂ isotherm in the absolute pressure range 100-200 mmHg. Similarly, SOFOUR-2-Zn revealed inflections at 350-400 mmHg in the CO_2 at 195 K isotherm (Fig. 2a), and at 5-10 mm Hg in the N_2 at 77 K isotherm (Fig. S9†). Such an inflection was not observed in the 273 K and 298 K CO2 and C₂H₂ isotherms (Fig. S10 and S11†). At 298 K, the CO₂ uptakes of SOFOUR-2-Zn and SIFSIX-24-Zn at 1 bar were observed to be 41 $cm^3 g^{-1}$ (1.78 mmol g^{-1}) and 40 $cm^3 g^{-1}$ (1.79 mmol g^{-1}), respectively (Fig. 2b). The $Q_{\rm st}$ values for CO_2 , 22.1 kJ ${\rm mol}^{-1}$ and 16.8 kJ mol⁻¹, respectively, at low loading (Fig. 2c and S12†) are

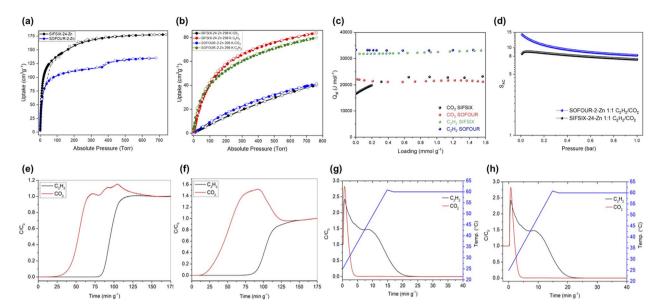


Fig. 2 Gas sorption properties of SIFSIX-24-Zn and SOFOUR-2-Zn: (a) 195 K CO_2 ; (b) 298 K C_2H_2 and CO_2 , (c) Q_{st} for C_2H_2 and CO_2 . (d) IAST selectivity for C_2H_2 over CO_2 at 298 K and 1:1(v/v) mixture; (e) breakthrough curve at 298 K for 1:1 C_2H_2/CO_2 mixture for SOFOUR-22-Zn; (f) breakthrough curve at 298 K for 1:1 C_2H_2/CO_2 mixture for SIFSIX-24-Zn; (g) temperature programmed desorption after breakthrough experiment for SOFOUR-2-Zn; (h) temperature programmed desorption after breakthrough experiment for SIFSIX-24-Zn.

exceptionally low. In contrast, the uptakes for C_2H_2 at 298 K were relatively high, 79 and 84 cm³ g⁻¹, or 3.52 and 3.75 mmol g⁻¹, respectively (Fig. 2b), with $Q_{\rm st}$ values of 33.3 kJ mol⁻¹ and 31.8 kJ mol⁻¹, respectively, at low loading.⁵⁴ Evidently both these sorbents exhibit a relatively high pure component uptake for C_2H_2 over CO_2 at 298 K, which is in the range that could break the usual trade-off between uptake and selectivity.^{55,56} PXRD patterns measured after activation and adsorption experiments showed retention of the crystal structures of both materials (Fig. S13†).

Since single-component gas sorption isotherms revealed significantly higher C₂H₂ uptakes relative to CO₂, ideal adsorbed solution theory (IAST) was applied using the pyIAST Python package 57 to determine the selectivity for $\mathrm{C_2H_2}$ in a 1:1 $\mathrm{C_2H_2/}$ CO_2 mixture, S_{AC} . We found moderate selectivities for **SOFOUR**-2-Zn and SIFSIX-24-Zn of 8.2 and 7.3 at 1 bar and 298 K, respectively (Fig. 2d and S14†). Although these selectivity numbers are lower than benchmark physisorbents such as ZNU-1 (56.6),⁵⁸ Zn₂(bpy)(btec) (33.3),⁵⁹ sql-16-Cu-NO₃-α (27.8),⁶⁰ and Ni₃(HCOO)₆ (22),⁶¹ they are higher than HUMs such as TIFSIX-2-Ni-i (6.1),62 and NbOFFIVE-3-Ni (6.0)56 (see Table S5† for a list of leading C₂H₂/CO₂ selective PCNs). Combining both IAST selectivity and adsorption capacity recorded at 298 K, the separation potentials for both sorbents were found to be similar at 1 bar and 298 K: 0.78 mmol g⁻¹ for SOFOUR-2-Zn, and $0.76 \text{ mmol g}^{-1} \text{ for SIFSIX-24-Zn (Fig. S15}^{\dagger}).$

The water vapour sorption isotherm of **SOFOUR-2-Zn** reveals a sigmoidal adsorption profile with a total uptake approaching 30 wt% at 95% R.H. (relative humidity), followed by desorption with low hysteresis. In contrast, **SIFSIX-24-Zn** shows a sudden decrease in uptake at *ca.* 90% R.H., followed by high desorption hysteresis, typical of moisture-induced phase degradation (Fig. S16†). Accelerated stability tests conducted by incubating

activated samples at 40 °C and 75% R.H. show retention of the porous phase of **SOFOUR-2-Zn** over 5 days, whereas significant new peaks are observed in **SIFSIX-24-Zn** within 90 hours of exposure (Fig. S17†), indicating that the SO_4^{2-} pillar enhances framework stability relative to SiF_6^{2-} .

Dynamic column breakthrough testing. Encouraged by the single-component gas sorption data, we performed dynamic column breakthrough (DCB) experiments on microcrystalline samples of SOFOUR-2-Zn and SIFSIX-24-Zn. A 1:1 C₂H₂/CO₂ mixture was passed through a column packed with activated sample under a total flow rate of 1.0 sccm and the effluent composition was monitored using mass spectrometry. For SOFOUR-2-Zn (Fig. 2e), CO2 breakthrough occurred at 25.4 min g^{-1} , followed by C_2H_2 at 81.0 min g^{-1} (55.6 min g^{-1} later). During this interval, the minimum effluent purity of CO₂ was measured to be 99.989% and the saturation uptakes were 47.1 cm³ g⁻¹ and 23.2 cm³ g⁻¹ for C₂H₂ and CO₂, respectively, resulting in a separation factor (α_{AC}) of 2.05. For SIFSIX-24-Zn (Fig. 2f), CO_2 breakthrough occurred at 14.2 min g^{-1} with a minimum effluent purity of 99.991% and C₂H₂ breakthrough occurred at 78.6 min g^{-1} (64.4 min g^{-1} later). Minor fluctuations were observed at the onset of gas breakthrough in all experiments due to a pressure drop across the powdered sorbent bed. The saturation uptakes for C₂H₂ and CO₂ were determined to be 53.0 cm³ g⁻¹ and 10.1 cm³ g⁻¹, respectively (Table S6†), resulting in higher α_{AC} of 5.26, putting SIFSIX-24-Zn in the same performance range as TIFSIX-4-Cu in terms of separation factor and pure component C_2H_2 uptake (5.4 and 3.85 mmol g^{-1} , respectively).56

Temperature Programmed Desorption (TPD) experiments were conducted after completion of the adsorption branches in DCB experiments for both **SOFOUR-2-Zn** and **SIFSIX-24-Zn** (Fig. 2g and h) by replacing the inlet gas mixture flow with 20

sccm of He and applying a temperature ramp of 5 °C min⁻¹ from 25 °C to 60 °C. Desorption was continued until no further adsorbate was detected. We found that 60 °C was sufficient to regenerate both HUMs. Similar TPD curves were obtained for both SOFOUR-2-Zn and SIFSIX-24-Zn, characterised by rapid decreases in effluent CO₂ concentration, while C₂H₂ continued to be released with increasing temperature for a period prior to desorption. Fuel grade C₂H₂ (>98% purity) was eluted in the interval between 5 and 27 min g^{-1} for SIFSIX-24-Zn, and between 4 and 20 min g^{-1} for SOFOUR-2-Zn, corresponding to productivities of 9.45 L kg⁻¹ and 7.69 L kg⁻¹ of fuel grade C₂H₂ respectively, and peak C2H2 purities of 99.66 and 99.92%, respectively (Table S7†). These results are similar to literature values in terms of peak C2H2 purity for TIFSIX-2-Cu-i,63 SIFSIX-22-Zn and SOFOUR-1-Zn,22 which are all 99.9% or higher. The productivities for fuel grade C2H2 in a 1:1 C2H2/CO2 mixture are 9.45 L kg^{-1} and 7.69 L kg^{-1} for SIFSIX-24-Zn and SOFOUR-2-Zn, respectively. This is much higher than previously reported values of 3.3 L kg⁻¹ and 3.1 L kg⁻¹, for SIFSIX-22-Zn and SOFOUR-1-Zn, respectively.22 SOFOUR-2-Zn and SIFSIX-24-Zn also produced significant amounts of high purity C₂H₂ (99.5%). For SIFSIX-24-Zn, >99.5% C₂H₂ eluted over the interval 5.8 to 23.9 min g⁻¹, resulting in a productivity of 8.75 L kg⁻¹, only 0.7 L kg⁻¹ less than the production of fuel-grade >98% C₂H₂, but for SOFOUR-2-Zn, >99.5% C₂H₂ was eluted only between 5.3 and 9.4 min g⁻¹ resulting in a significantly lower productivity of 3.01 L kg⁻¹. These values are lower than the benchmark of 53.8 L kg $^{-1}$ for >99.5% C₂H₂ set by **ZNU-1**. Additional DCB experiments conducted using a humid C2H2/CO2 mixture showed that separation performance was largely unaffected by moisture in both SOFOUR-2-Zn and SIFSIX-24-Zn over a complete adsorption cycle, despite the poor stability of SIFSIX-

Based on pure component isotherms and IAST calculations, both **SOFOUR-2-Zn** and **SIFSIX-24-Zn** should have roughly the same performance. However, DCB experiments revealed that despite showing comparable C_2H_2 uptakes in mixed-gas conditions, **SIFSIX-24-Zn** is better in terms of separation factor (2.05 vs. 5.26 for **SOFOUR-2-Zn** and **SIFSIX-24-Zn**, respectively). Production of high purity (>99.5%) C_2H_2 was also higher for **SIFSIX-24-Zn** than for **SOFOUR-2-Zn**, although, fuel-grade (>98%) productivity was similar for both. The differences might be attributed to the weaker Q_{st} for CO_2 of **SIFSIX-24-Zn**, 16.8 kJ mol⁻¹ (ΔQ_{st} for $C_2H_2/CO_2 = 15.0$ kJ mol⁻¹), vs. 22.1 kJ mol⁻¹ (ΔQ_{st} for $C_2H_2/CO_2 = 11.2$ kJ mol⁻¹) for **SOFOUR-2-Zn**.

Sorbate binding sites

24-Zn towards moisture (Fig. S18†).

To better understand the nature of the C_2H_2 and CO_2 binding sites, density functional theory (DFT) calculations were performed for **SOFOUR-2-Zn** and **SIFSIX-24-Zn** (see ESI† for computational methodology). In **SOFOUR-2-Zn**, the C_2H_2 molecule orients along one of the channel walls, forming simultaneous hydrogen bonds from both C–H hydrogen atoms to $SO_4^{\ 2^-}$ oxygen atoms, with O···H distances of 2.57 Å and 2.62 Å (Fig. 3). In **SIFSIX-24-Zn**, hydrogen bonds are bifurcated, with the H-atoms being shared between two F-atoms of the same

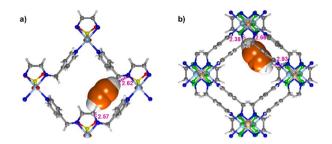


Fig. 3 Ball and stick models of (a) the C_2H_2 binding site for SOFOUR-2-Zn; (b) the C_2H_2 binding site for SIFSIX-24-Zn. Short contacts are highlighted as dashed magenta bonds and distances are given in Å.

SIFSIX pillar, with distances of 2.38 and 2.66 Å on one end, and 2.93 Å with a contact of 3.66 Å on the other end (Fig. 3). These multi-site short contacts provide a clear basis for the selective C_2H_2 binding observed in both materials. In contrast, CO_2 binding sites are primarily governed by electrostatic interactions between the CO_2 carbon and electronegative pillar F and O atoms respectively (Fig. S19†). DFT-derived enthalpy values associated with gas adsorption are presented in Table S8.†

Conclusions

The previously reported material $[Zn(enmepy)(SO_4)]_n$ (SOFOUR-2-Zn),46 illustrates the potential utility of en based ligands for design of new HUMs with potential utility in gas separations. Pillar substitution using a crystal engineering approach enabled us to isolate $[Zn(enmepy)(SiF_6)]_n$ (SIFSIX-24-Zn), the prototypal member of a new platform of MFSIX HUMs. Pure component gas sorption studies and dynamic column breakthrough experiments revealed strong performance for the separation of C₂H₂ from CO₂ for both HUMs with appreciable amounts of fuel grade C₂H₂ (>98%) as shown by temperature programmed desorption of the sorbed gases from a 1:1 mixture of C_2H_2/CO_2 . Productivities of 9.45 L kg^{-1} and 7.69 L kg^{-1} were measured for SIFSIX-24-Zn and SOFOUR-2-Zn, respectively, and SIFSIX-24-Zn produced high purity C₂H₂ (>99.5%). This study demonstrates for the first time that chelating ethylenediamine based ligands can sustain facile to synthesise HUMs with strong gas separation properties. Both HUM platforms are inherently modular and their scope in terms of composition and properties are under further investigation in our laboratory. We anticipate that SIFSIX-24-Zn and SOFOUR-2-Zn will serve as prototypes for families of second-generation sorbents through metal and/or pillar substitution, as well as ligand modification.

Data availability

The data supporting the findings of this study are available in the ESI† or from the authors upon request.

Author contributions

Project conceptualisation: D. J. O., D. S., S. M. and M. J. Z.; synthesis and characterisation: D. J. O., A. R. and A. A. B.; single component gas sorption: D. S., A. R. and D. J. O.; dynamic

column breakthrough and temperature programmed desorption: D. S. and S. M.; molecular modelling: M. V.; single crystal X-ray crystallography: D. J. O.; Cambridge Structural Database analysis: D. J. O. and A. R.; writing – original draft: D. J. O., D. S., S. M., A. A. B., and M. J. Z.; writing – review & editing: all authors; funding acquisition: M. J. Z. and M. V.; supervision: S. M., M. J. Z. and M. V. D. J. O., D. S. and A. R. contributed equally to this

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We gratefully acknowledge Science Foundation Ireland (16/IA/4624, and 12/RC/2278_P2) and the European Research Council (ADG885695). M. V. acknowledges the Irish Centre for High-End Computing (ICHEC) for the provision of computational facilities and support. Amin Koochaki is acknowledged for useful discussions and preliminary modelling studies. S. M. acknowledges an SFI-IRC Pathway award (21/PATH-S/9454) from the Science Foundation Ireland.

Notes and references

- 1 W. Mori, F. Inoue, K. Yoshida, H. Nakayama, S. Takamizawa and M. Kishita, *Chem. Lett.*, 1997, 26, 1219–1220.
- 2 M. Kondo, T. Yoshitomi, H. Matsuzaka, S. Kitagawa and K. Seki, *Angew. Chem., Int. Ed.*, 1997, **36**, 1725–1727.
- 3 H. Li, M. Eddaoudi, T. L. Groy and O. M. Yaghi, *J. Am. Chem. Soc.*, 1998, **120**, 8571–8572.
- 4 X. Zhao, Y. Wang, D.-S. Li, X. Bu and P. Feng, *Adv. Mater.*, 2018, **30**, 1705189.
- 5 J.-R. Li, R. J. Kuppler and H.-C. Zhou, *Chem. Soc. Rev.*, 2009, 38, 1477–1504.
- 6 S. Mukherjee, D. Sensharma, K.-J. Chen and M. J. Zaworotko, Chem. Commun., 2020, 56, 10419–10441.
- 7 L. Yang, S. Qian, X. Wang, X. Cui, B. Chen and H. Xing, *Chem. Soc. Rev.*, 2020, 49, 5359–5406.
- 8 G. Verma, J. Ren, S. Kumar and S. Ma, *Eur. J. Inorg. Chem.*, 2021, **2021**, 4498–4507.
- 9 D. Zhao, K. Yu, X. Han, Y. He and B. Chen, *Chem. Commun.*, 2022, **58**, 747–770.
- 10 P. Nugent, Y. Belmabkhout, S. D. Burd, A. J. Cairns, R. Luebke, K. Forrest, T. Pham, S. Ma, B. Space, L. Wojtas, M. Eddaoudi and M. J. Zaworotko, *Nature*, 2013, 495, 80–84.
- 11 S. Mukherjee and M. J. Zaworotko, *Trends Chem.*, 2020, 2, 506–518.
- 12 K. Uemura, A. Maeda, T. K. Maji, P. Kanoo and H. Kita, *Eur. J. Inorg. Chem.*, 2009, **2009**, 2329–2337.
- 13 A. Kumar, C. Hua, D. G. Madden, D. O'Nolan, K.-J. Chen, L.-A. J. Keane, J. J. Perry and M. J. Zaworotko, *Chem. Commun.*, 2017, 53, 5946–5949.
- 14 S. Mukherjee, N. Kumar, A. A. Bezrukov, K. Tan, T. Pham, K. A. Forrest, K. A. Oyekan, O. T. Qazvini, D. G. Madden,

- B. Space and M. J. Zaworotko, *Angew. Chem., Int. Ed.*, 2021, **60**, 10902–10909.
- 15 N. C. Harvey-Reid, D. Sensharma, S. Mukherjee, K. M. Patil, N. Kumar, S. J. Nikkhah, M. Vandichel, M. J. Zaworotko and P. E. Kruger, *ACS Appl. Mater. Interfaces*, 2024, **16**, 4803–4810.
- 16 H. S. Scott, A. Bajpai, K.-J. Chen, T. Pham, B. Space, J. J. Perry and M. J. Zaworotko, *Chem. Commun.*, 2015, 51, 14832– 14835.
- 17 H. S. Scott, N. Ogiwara, K.-J. Chen, D. G. Madden, T. Pham, K. Forrest, B. Space, S. Horike, J. J. Perry Iv, S. Kitagawa and M. J. Zaworotko, *Chem. Sci.*, 2016, 7, 5470–5476.
- 18 P. M. Bhatt, Y. Belmabkhout, A. Cadiau, K. Adil, O. Shekhah, A. Shkurenko, L. J. Barbour and M. Eddaoudi, *J. Am. Chem. Soc.*, 2016, 138, 9301–9307.
- 19 A. Cadiau, K. Adil, P. M. Bhatt, Y. Belmabkhout and M. Eddaoudi, *Science*, 2016, 353, 137–140.
- 20 A. Cadiau, Y. Belmabkhout, K. Adil, P. M. Bhatt, R. S. Pillai, A. Shkurenko, C. Martineau-Corcos, G. Maurin and M. Eddaoudi, *Science*, 2017, 356, 731–735.
- 21 M. H. Mohamed, S. K. Elsaidi, T. Pham, K. A. Forrest, B. Tudor, L. Wojtas, B. Space and M. J. Zaworotko, *Chem. Commun.*, 2013, 49, 9809–9811.
- 22 D. Sensharma, D. J. O'Hearn, A. Koochaki, A. A. Bezrukov, N. Kumar, B. H. Wilson, M. Vandichel and M. J. Zaworotko, Angew. Chem., Int. Ed., 2022, 61, e202116145.
- 23 J. Wang, Y. Zhang, Y. Su, X. Liu, P. Zhang, R.-B. Lin, S. Chen, Q. Deng, Z. Zeng, S. Deng and B. Chen, *Nat. Commun.*, 2022, 13, 200.
- 24 R.-B. Lin, L. Li, H. Wu, H. Arman, B. Li, R.-G. Lin, W. Zhou and B. Chen, *J. Am. Chem. Soc.*, 2017, **139**, 8022–8028.
- 25 H. S. Scott, M. Shivanna, A. Bajpai, D. G. Madden, K.-J. Chen, T. Pham, K. A. Forrest, A. Hogan, B. Space, J. J. Perry Iv and M. J. Zaworotko, ACS Appl. Mater. Interfaces, 2017, 9, 33395– 33400.
- 26 M. Shivanna, K.-i. Otake, B.-Q. Song, L. M. van Wyk, Q.-Y. Yang, N. Kumar, W. K. Feldmann, T. Pham, S. Suepaul, B. Space, L. J. Barbour, S. Kitagawa and M. J. Zaworotko, *Angew. Chem., Int. Ed.*, 2021, 60, 20383–20390.
- 27 S. K. Elsaidi, M. H. Mohamed, T. Pham, T. Hussein, L. Wojtas, M. J. Zaworotko and B. Space, *Cryst. Growth Des.*, 2016, 16, 1071–1080.
- 28 Q. Lin, C. Mao, A. Kong, X. Bu, X. Zhao and P. Feng, *J. Mater. Chem. A*, 2017, 5, 21189–21195.
- 29 L. He, J. K. Nath and Q. Lin, *Chem. Commun.*, 2019, 55, 412–415.
- 30 Q.-L. Qian, X.-W. Gu, J. Pei, H.-M. Wen, H. Wu, W. Zhou, B. Li and G. Qian, J. Mater. Chem. A, 2021, 9, 9248–9255.
- 31 S. Zou, Z. Di, Y. Liu, Z. Ji, H. Li, C. Chen and M. Wu, *Inorg. Chem. Commun.*, 2022, **137**, 109198.
- 32 Y. Liu, Y. Zhang, P. Zhang, Y. Peng, X. Liu, J. Chen, S. Chen, Z. Zeng, J. Wang and S. Deng, *Chem. Eng. Process.*, 2022, 172, 108768.
- 33 J. Liu, H. Shuai, J. Chen, S. Chen, Z. Zhou, J. Wang and S. Deng, *Chem & Bio Eng.*, 2024, **1**, 83–90.

34 D. Sensharma, B. H. Wilson, N. Kumar, D. J. O'Hearn and M. J. Zaworotko, *Cryst. Growth Des.*, 2022, 22, 5472–5480.

Edge Article

- 35 Y. H. Andaloussi, D. Sensharma, A. A. Bezrukov, D. C. Castell, T. He, S. Darwish and M. J. Zaworotko, *Cryst. Growth Des.*, 2024, 24, 2573–2579.
- 36 X. Liu, P. Zhang, H. Xiong, Y. Zhang, K. Wu, J. Liu, R. Krishna, J. Chen, S. Chen, Z. Zeng, S. Deng and J. Wang, *Adv. Mater.*, 2023, 35, 2210415.
- 37 C. R. Groom, I. J. Bruno, M. P. Lightfoot and S. C. Ward, *Acta Crystallogr.*, *Sect. B: Struct. Sci., Cryst. Eng. Mater.*, 2016, 72, 171–179.
- 38 J. Haníková, J. Černák, J. Kuchár and E. Čižmár, *Inorg. Chim. Acta*, 2012, 385, 178–184.
- 39 J. Lhoste, K. Adil, A. Le Bail, M. Leblanc, A. Hémon-Ribaud and V. Maisonneuve, *J. Fluor. Chem.*, 2012, **134**, 29–34.
- 40 P. C. Healy, C. H. L. Kennard, G. Smith and A. H. White, *Cryst. Struct. Commun.*, 1978, 7, 565–570.
- 41 V. Manríquez, M. Campos-Vallette, N. Lara, N. González-Tejeda, O. Wittke, G. Díaz, S. Diez, R. Muñoz and L. Kriskovic, J. Chem. Crystallogr., 1996, 26, 15–22.
- 42 M. K. Taylor, D. E. Stevenson, L. E. A. Berlouis, A. R. Kennedy and J. Reglinski, *J. Inorg. Biochem.*, 2006, **100**, 250–259.
- 43 O. V. Kravchina, A. I. Kaplienko, E. P. Nikolova, A. G. Anders, D. V. Ziolkovskii, A. Orendachova and M. Kajnakova, *Russ. J. Phys. Chem.*, 2011, 5, 209–214.
- 44 M. Lutz, S. Smeets and P. Parois, *Acta Crystallogr., Sect. E: Crystallogr. Commun.*, 2010, **66**, m671–m672.
- 45 M. Kajňaková, A. Orendáčová, M. Orendáč, A. Feher, M. Mal'arová and Z. Trávníček, *Acta Phys. Pol.*, 2008, 113, 507–510.
- 46 Y. Wen, T. Sheng, Z. Sun, Z. Xue, Y. Wang, Y. Wang, S. Hu, X. Ma and X. Wu, Chem. Commun., 2014, 50, 8320–8323.
- 47 Y. Wen, T. Sheng, X. Zhu, C. Zhuo, S. Su, H. Li, S. Hu, Q.-L. Zhu and X. Wu, *Adv. Mater.*, 2017, **29**, 1700778.
- 48 S. Khatua, A. Santra, S. Padmakumar, K. Tomar and S. Konar, *ChemistrySelect*, 2018, 3, 785–793.
- 49 C. F. Macrae, I. Sovago, S. J. Cottrell, P. T. A. Galek, P. McCabe, E. Pidcock, M. Platings, G. P. Shields, J. S. Stevens, M. Towler and P. A. Wood, *J. Appl. Crystallogr.*, 2020, 53, 226–235.

- 50 A. Spek, Acta Crystallogr., Sect. C: Struct. Chem., 2015, 71, 9-18.
- 51 Y. Wen, T. Sheng, S. Hu, X. Ma, C. Tan, Y. Wang, Z. Sun, Z. Xue and X. Wu, *Chem. Commun.*, 2013, 49, 10644–10646.
- 52 Y. Wen, T. Sheng, S. Hu, Y. Wang, C. Tan, X. Ma, Z. Xue, Y. Wang and X. Wu, CrystEngComm, 2013, 15, 2714–2721.
- 53 Y. Wen, T. Sheng, C. Zhuo, X. Zhu, S. Hu, W. Cao, H. Li, H. Zhang and X. Wu, *Inorg. Chem.*, 2016, 55, 4199–4205.
- 54 A. Nuhnen and C. Janiak, *Dalton Trans.*, 2020, **49**, 10295–10307.
- 55 N. Kumar, S. Mukherjee, N. C. Harvey-Reid, A. A. Bezrukov, K. Tan, V. Martins, M. Vandichel, T. Pham, L. M. van Wyk, K. Oyekan, A. Kumar, K. A. Forrest, K. M. Patil, L. J. Barbour, B. Space, Y. Huang, P. E. Kruger and M. J. Zaworotko, *Chem*, 2021, 7, 3085–3098.
- 56 D. M. Venturi, M. S. Notari, R. Bondi, E. Mosconi, W. Kaiser, G. Mercuri, G. Giambastiani, A. Rossin, M. Taddei and F. Costantino, ACS Appl. Mater. Interfaces, 2022, 14, 40801– 40811.
- 57 C. M. Simon, B. Smit and M. Haranczyk, *Comput. Phys. Commun.*, 2016, **200**, 364–380.
- 58 L. Wang, W. Sun, Y. Zhang, N. Xu, R. Krishna, J. Hu, Y. Jiang, Y. He and H. Xing, *Angew. Chem., Int. Ed.*, 2021, **60**, 22865– 22870.
- 59 Y. Chen, Y. Du, Y. Wang, R. Krishna, L. Li, J. Yang, J. Li and B. Mu, AIChE J., 2021, 67, e17152.
- 60 N. Kumar, S. Mukherjee, A. A. Bezrukov, M. Vandichel, M. Shivanna, D. Sensharma, A. Bajpai, V. Gascón, K.-i. Otake, S. Kitagawa and M. J. Zaworotko, *SmartMat*, 2020, 1, e1008.
- 61 L. Zhang, K. Jiang, J. Zhang, J. Pei, K. Shao, Y. Cui, Y. Yang, B. Li, B. Chen and G. Qian, ACS Sustain. Chem. Eng., 2019, 7, 1667–1672.
- 62 M. Jiang, X. Cui, L. Yang, Q. Yang, Z. Zhang, Y. Yang and H. Xing, Chem. Eng. J., 2018, 352, 803–810.
- 63 K.-J. Chen, H. S. Scott, D. G. Madden, T. Pham, A. Kumar, A. Bajpai, M. Lusi, K. A. Forrest, B. Space, J. J. I. V. Perry and M. J. Zaworotko, *Chem*, 2016, 1, 753–765.