# Chemical Science



# **EDGE ARTICLE**

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2024, 15, 16688

dll publication charges for this article have been paid for by the Royal Society of Chemistry

Received 18th June 2024 Accepted 9th September 2024

DOI: 10.1039/d4sc04001e

rsc.li/chemical-science

# Stabilizing ultra-close Pt clusters on all-in-one CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes against sintering†

Wanlin Fu, Da Kuibo Yin, Db Zhihui Li, Da Jun Wang, Mingyu Tang, Jilan Tian, Litao Sun, Db Yueming Sunb and Yungian Dai Da A

Metal sintering poses significant challenges for developing reliable catalytic systems toward high-temperature reactions, particularly those based on metal clusters with sizes below 3 nm. In this work, electrospun dual-oxide fibril-in-tubes consisting of CeO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> are rationally designed in an all-in-one manner, to stabilize 2.3 nm Pt clusters with a Tammann temperature (sintering onset temperature) lower than 250 °C. The abundant pores and channels effectively stabilize the Pt clusters physically, while the strong support, CeO<sub>2</sub>, with high adhesion, pins Pt clusters firmly, and the adjacent weak support, Al<sub>2</sub>O<sub>3</sub>, with low adhesion, provides energy barriers to prevent the clusters and emitted Pt atom(s) from moving across the support. Therefore, the ultra-close 2.3 nm Pt clusters, featuring an average nearest neighboring distance of only 2.1 nm, were carefully stabilized against sintering at temperatures exceeding 750 °C, even in oxidative and steam-containing environments. In addition, this catalytic system can efficiently and durably serve in diesel combustion, a high-temperature exothermic reaction, showing no activity decline after 5 cycles. This work provides a comprehensive understanding of sinter-resistant catalytic systems, and presents new insights for the development of advanced nanocatalysts.

# 1 Introduction

In the past several decades, the development of nanoscience has enabled the precise manipulation of surfaces and interfaces of catalysts in the nanometer size regime and gives rise to a superior cornerstone for energy conversion and environmental protection.1 To maximize the mass-specific activity, bulky metals are generally dispersed into nanoparticles (typically >3 nm) and even isolated as clusters (usually <3 nm) or single atoms on specific supports.2 However, as the size of the metal decreases, the increasing surface energy presents a significant tendency for metal sintering (growing into larger clusters and/or particles).3 Taking 3 nm Pt nanoparticles as an example, the Tammann temperature, at which sintering initiates, could decrease to below 250 °C, which is extremely lower than that of the bulky Pt (749 °C).4 In this case, highly dispersed metal species suffered substantial deactivation during hightemperature reactions, such as the diesel combustion (600-800 °C), propane dehydrogenation (590-630 °C), and the dry reformation of methane (800–1000 °C). Besides, reaction exotherm can cause the local temperature of active sites far beyond

that of the surroundings, leading to preferential damage of these most active atoms. Therefore, mitigating catalyst sintering is of significant importance for the successful translation of well-defined nanocatalysts from laboratory to industrial application, yet it remains highly challenging.

The sintering pathways of metal nanoparticles are commonly dominated by both particle migration and coalescence (PMC) and Ostwald ripening (OR), either simultaneously or alternatively.3 Through the PMC pathway, metal nanoparticles would migrate across the support via Brownian-like motion, until they meet and merge into a larger particle.6 As for the OR mechanism, metal atoms leave the surface of one nanoparticle with a higher chemical potential to join another nanoparticle with a lower chemical potential.3 As such, the sinter-resistance relies deeply on the metal loading density on supports, because of the fact that mass transport through surface diffusion and/or migration of the metal species could be facilitated if the distance between adjacent species is shortened.7 Admittedly, employing porous supports with a high surface area could slow down the metal sintering by enlarging the neighboring distance. However, these porous supports would suffer from densification due to the excessive surface free energy, and then dramatically shorten the neighboring distance for supported metal species. Therefore, it is still an imperative challenge to stabilize metal clusters on reliable supports, especially for those in ultra-close proximity.

To mitigate sintering, great efforts have been devoted to stabilizing metals physically and/or chemically. So far,

<sup>&</sup>quot;School of Chemistry and Chemical Engineering, Southeast University, Nanjing, Jiangsu 211189, China. E-mail: daiy@seu.edu.cn

<sup>&</sup>lt;sup>b</sup>SEU-FEI Nano-Pico Center, Key Laboratory of MEMS of Ministry of Education, School of Electronic Science and Engineering, Southeast University, Nanjing, Jiangsu 211189, China

<sup>†</sup> Electronic supplementary information (ESI) available. See DOI: https://doi.org/10.1039/d4sc04001e



Fig. 1 Schematic illustration of the physical and chemical stabilization mechanisms for Pt clusters on the  $CeO_2/Al_2O_3$  fibril-in-tubes in close proximity.

embedding metals in a hollow and/or porous matrix, such as silica, 8-10 zeolites, 11 or CeO<sub>2</sub> (ref. 12) has been explored as an efficient approach toward sinter-resistant nanocatalysts. Alternatively, enhancing the metal–support interaction through tailoring the interface structure, composition, lattice match, charge rearrangement, *etc*, contributes to fascinating progress for stabilizing metals without any protective shell. 13 However, recent theoretical work revealed that too-strong metal–support interaction triggered rapid OR, whereas too-weak metal–support interaction stimulated facile PMC, both of which severely worsened the thermal stability. 6 Dual-oxide supports hold great promise to mitigate the metal sintering, but are still overwhelmed by the challenge in facile fabrication with controlled composition and dispersity at the nanoscale.

In this work, 2.3 nm Pt clusters in ultra-close proximity were well stabilized on CeO2/Al2O3 fibril-in-tubes, achieving boosted sintering resistance over 750 °C in an oxidative and steamcontaining atmosphere. As shown in Fig. 1, the abundant inter-grain pores and elegant fibril-in-tube structure effectively stabilize the Pt clusters physically. Chemically, the strong support, CeO<sub>2</sub>, with higher adhesion pins Pt clusters firmly (i.e., mitigating cluster migration and coalescence), while the integration of adjacent weak support, Al<sub>2</sub>O<sub>3</sub>, with lower adhesion to Pt, provides energy barriers at the dual-oxide interfaces, and thus energetically prevent the clusters and emitted Pt atom(s) from moving across the support. The sintering behavior of Pt clusters on CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes was dynamically monitored by in situ HAADF-STEM investigation. Moreover, we also demonstrated the superior performance of the Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst for diesel combustion, in terms of both activity and durability.

# 2 Experimental section

#### 2.1 Materials

Polyvinylpyrrolidone (PVP,  $M_{\rm w}\approx 1.3\times 10^6$  or  $5.5\times 10^4$ ), chloroplatinic acid hydrate ( ${\rm H_2PtCl_6\cdot xH_2O}$ , 99.995%), cerium acetylacetone (Ce(acac)<sub>3</sub>), and aluminum acetylacetonate (Al(acac)<sub>3</sub>) were obtained from Alfa Aesar. The model soot used is Printex-U (Degussa Corporation). All chemicals were used as received. The water used in all the experiments was filtered through a Millipore filtration system with a resistivity of 18 M $\Omega$  cm.

# 2.2 Fabrication of fibril-in-tube CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> nanofibers by single-spinneret electrospinning

The composite nanofibers were prepared by electrospinning a precursor containing 0.187 g of Al(acac)<sub>3</sub>, 0.3 g of Ce(acac)<sub>3</sub>, 0.4 g of PVP ( $M_{\rm w}\approx 1.3\times 10^6$ ), and 6 mL of ethanol with a flow rate of 0.5 mL h<sup>-1</sup>, at 15 kV. Before electrospinning, the precursor was sonicated for 20 min, to achieve better homogeneity. The as-spun Ce(acac)<sub>3</sub>/Al(acac)<sub>3</sub>/PVP nanofibers were converted to CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes after calcination at 500 ° C for 2 h in air with a ramping rate of 4.2 °C min<sup>-1</sup>.

#### 2.3 Fabrication of CeO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> nanofibers

The CeO<sub>2</sub> nanofibers were prepared by electrospinning a precursor containing 0.3 g of Ce(acac)<sub>3</sub>, 0.6 g of PVP ( $M_{\rm w}\approx 1.3\times 10^6$ ), 3 mL of acetone, and 3 mL of ethanol with a flow rate of 0.5 mL h<sup>-1</sup>, at 15 kV. The as-spun Ce(acac)<sub>3</sub>/PVP nanofibers were then calcined at 500 °C for 2 h in air with a ramping rate of 4.2 °C min<sup>-1</sup>. The Al<sub>2</sub>O<sub>3</sub> nanofibers were prepared by electrospinning a precursor containing 0.3 g of Al(acac)<sub>3</sub>, 0.3 g of PVP ( $M_{\rm w}\approx 1.3\times 10^6$ ), 3 mL of acetone, and 2 mL of ethanol with a flow rate of 0.3 mL h<sup>-1</sup>, at 15 kV. The as-spun Al(acac)<sub>3</sub>/PVP nanofibers were kept in air overnight followed by calcination at 500 °C for 2 h in air with a ramping rate of 4.2 °C min<sup>-1</sup>.

#### 2.4 Synthesis of Pt clusters

Pt clusters were prepared by a polyol method. Typically, 4 mL of ethylene glycol was added to a glass vial and heated in an oil bathtub at 110 °C for 30 min. Then, 22.5 mg of PVP ( $M_{\rm w}\approx55\,$ 000) and 16.5 mg of  ${\rm H_2PtCl_6}$  were dissolved separately in 2 mL of ethylene glycol at room temperature. 0.5 mL of each solution was then added simultaneously into the system at a rate of 0.67 mL min<sup>-1</sup>. The reaction continued with heating at 110 °C and was stopped when the color changed from yellow to light brown. The as-obtained Pt clusters were then cooled down to room temperature.

#### 2.5 Loading of Pt clusters

The as-prepared Pt clusters were loaded on the surface of different nanofibers by a simple impregnation method. First, 0.2 mL of Pt suspension was diluted into 2 mL of ethanol. Then,

5 mg of nanofibers were immersed in the 0.2 mL diluted Pt suspension, followed by a gentle stirring at room temperature for 2 h. The as-prepared sample was washed with ethanol six times. The centrifugation speed for washing was generally 6000-10000 rpm and each centrifugation lasted for 3 min. After centrifugation, the samples were dried in an oven at 40 °C.

#### 2.6 Dynamic observation

Dynamic observation of thermal stability of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> was conducted by an *in situ* heating experiment under an aberration-corrected transmission electron microscope (TEM, FEI Titan operating at 300 kV). In a typical procedure, a drop (3 μL) of catalyst-in-ethanol suspension was dropped on an electrical chip (E-chip). After the sample was dried, the E-chip was transferred to a heating holder (Aduro, Protochips Company) and inserted into the microscope chamber. As the nominal ramp rate of the heating holder can reach as high as 1000 °C ms<sup>-1</sup>, the temperatures of the sample are assumed to reach the set value immediately after switching on the current. The images were acquired in scanning-TEM (STEM) mode and a high-angle annular dark-field (HAADF) detector at low beam densities (typically, 60 A cm<sup>-2</sup>) was used to reduce the irradiation-induced sputtering effects.

#### 2.7 Catalytic elimination of soot particulates

A simulated model diesel soot sample was prepared by mixing Printex-U (the soot) with catalysts using a spatula for 5 min. The weight percent of soot was controlled to be around 10 wt%. To evaluate the soot combustion performance, a thermogravimetric analysis (TGA) of the soot combustion was performed using a thermogravimetric analyzer (Netzsch, STA449 F3) at a temperature ranging from room temperature to 900 °C with a flow rate of 100 mL min $^{-1}$ . The heating rate was 10 °C min $^{-1}$  in air (21% O2 and 79% N2). For the cycling reaction, a certain amount of Printex-U was added into the collected catalyst after each cycle of reaction, and the weight percent of soot was also controlled to be around 10 wt%.

#### 2.8 Characterization

Transmission electron microscopy (TEM) and high-resolution transmission electron microscopy (HRTEM) images were collected using transmission electron microscopes (Tecnai G2 T20, Talos, and Titan, FEI). Energy dispersive X-ray (EDX) mapping and high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) analysis were performed using a Talos. Aberration-corrected HAADF-STEM (AC-HAADF-STEM) images were obtained on a FEI Titan G2 60-300 STEM. SEM images were obtained using a field emission scanning electron microscope (FEI, Inspect F50) after coating the samples with Au. The ultra-thin slices were prepared by ultramicrotomy (LEICA EM UC7). Before characterization, non-woven CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes were cut into ultra-thin slices and dropped onto a Cu-grid coated with a carbon membrane. The crystal structure information was obtained with X-ray diffraction (XRD) (Bruker, D8 advance using Cu-K $\alpha$  radiation,  $\lambda = 1.5406$  Å). The Pt mass was determined using an Inductively Coupled

Plasma Optical Emission Spectrometer (ICP-OES) (Optima 7300DV, PerkinElmer Corporation). The Brunauer-Emmett-Teller (BET) surface area was obtained using a Nova 1200e (Quantachrome, U.S.A.). The binding energies were characterized using an X-ray photoelectron spectrometer (XPS, Escalab 250Xi, Thermo Fisher Scientific). The XPS spectra were analyzed by using Thermo Avantage software, based on the conventional Gaussian-based protocols. The defects were detected by Electron Paramagnetic Resonance (EPR) spectroscopy (A300, Bruker).

### 3 Results and discussion

# 3.1 Synthesis and structural characterization of $\text{CeO}_2/\text{Al}_2\text{O}_3$ fibril-in-tubes

The unusual CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes, with a Ce/Al dosage atomic ratio of 1.2, were conveniently fabricated by a costeffective and scalable single-spinneret electrospinning method, starting from a carefully designed precursor solution containing Ce(acac)<sub>3</sub>, Al(acac)<sub>3</sub>, PVP, and ethanol, followed by calcination at 500 °C in air (Fig. 2). According to the typical scanning electron microscope (SEM) and transmission electron microscopy (TEM) images (Fig. 2a, b and S1†), the external tube has an average diameter of ca. 275.9  $\pm$  54.0 nm, whereas the size of the fibril in the center is *ca.* 109.6  $\pm$  23.5 nm. The open channels between the fibril and tube, as well as the naturally formed inter-fiber pores (highlighted by the dashed lines in Fig. 2a), can greatly improve the mass transfer and enhance the trapping for reactants, thus being capable of accelerating the reaction kinetics. When serving as a substrate for metal species, the migration, and diffusion of metal species across different nanofibers, various surfaces within an individual fibril-in-tube, as well as adjacent accessible pores on the surface of the fibril-in-tube, can be hindered, thereby effectively enhancing the sinter-resistance of metal species.

In sharp contrast, the single-component CeO2 and Al2O3 nanofibers exhibited no fibril-in-tube morphology (Fig. S2†). When introducing a minute quantity of Al(acac)3, an observable transformation in the morphology of the obtained nanofibers (with a Ce/Al dosage molar ratio of 2.5) can be witnessed, transitioning from conventional columnar structures to desired fibril-in-tube configurations. However, when the Ce/Al molar ratio decreased to 0.8, the surface of dual-oxide nanofibers became extremely porous and rough, being more like the porous Al<sub>2</sub>O<sub>3</sub> nanofibers. Based on the thermogravimetry analysis and the temperature-dependent morphological evolution (Fig. S3†), it could be hypothesized that the formation of the fibril-in-tube structure might be contributed by the rapid and vigorous decomposition of Ce(acac)<sub>3</sub> and Al(acac)<sub>3</sub> together with the PVP matrix within the incredibly narrow temperature range. The rapid release of a large amount of gas could cause a huge pressure inside the columnar nanofibers, therefore, leaving a special channel within the fibril-in-tube structure.

The powder X-ray diffraction (XRD) results verified that the CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes are composed of fluorite CeO<sub>2</sub> and amorphous Al<sub>2</sub>O<sub>3</sub> (Fig. S4†).<sup>14</sup> Moreover, the Al<sup>3+</sup> cations may somehow dope into the CeO<sub>2</sub> crystal lattice, indicated by the peak shift of (111) toward a lower angle.<sup>15</sup> The calculated CeO<sub>2</sub> crystal size within CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes is as small as

**Edge Article** 

**Chemical Science** 

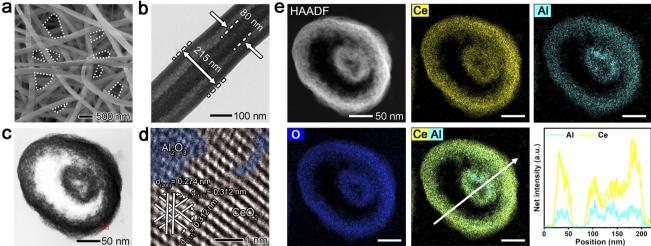


Fig. 2 (a) SEM image of  $CeO_2/Al_2O_3$  fibril-in-tubes. The dashed lines indicate the inter-fiber pores. (b) Typical TEM image of one individual  $CeO_2/Al_2O_3$  fibril-in-tubes. Al<sub>2</sub>O<sub>3</sub> fibril-in-tube. (c) TEM image collected on the cross-section of a single fibril-in-tube prepared with ultramicrotomy. (d) Inverse-FFT image of the HRTEM collected at the dashed squared area in (c).  $CeO_2$  and  $Al_2O_3$  were colored in red and blue respectively, for a better demonstration. (e) HAADF-STEM and the elemental mapping results investigated on the cross-section.

5.75 nm. Moreover, the CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes were endowed with enriched mesopores with diameters concentrated at 2.5 nm, 8.0 nm, and 20.5 nm (Fig. S5†). Specifically, the 2.5 nm mesopores, if accessible, could allow Pt clusters with a size below 3 nm to sit in steadily and therefore be isolated from each other. Meanwhile, the restricted small size of CeO2 could contribute to abundant grain boundaries, which could favor the robust anchoring of metal species.16

A careful investigation of the cross-section of CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes prepared by ultramicrotomy gave more detailed information about the spatial distribution of the two oxides (Fig. 2c-e). As shown, the cross-section of fibril-in-tubes whose axial direction is almost completely perpendicular to the ultrathin slice exhibited a concentric circular morphology (Fig. 2c). The high-resolution TEM (HRTEM) image (Fig. S6†) and the corresponding inverse Fast Fourier Transform (FFT) image (Fig. 2d) demonstrated that the CeO<sub>2</sub> exhibits a highly crystalline structure with lattice fringes of 0.312 and 0.274 nm, which can be indexed to the {111} and {200} planes of fluorite CeO<sub>2</sub>, respectively.17 However, the interstitial spaces between neighboring CeO<sub>2</sub> nanograins are filled with amorphous Al<sub>2</sub>O<sub>3</sub>. The HAADF-STEM image and the elemental mappings suggested homogeneous distributions of Ce, Al, and O elements (Fig. 2e). This can be understood by considering the inter-doping of Al and Ce atoms into the lattices of their respective oxide nanocrystals, which has been observed in our previous study on TiO2/Al2O3 nanofibers.18 Therefore, the highly and uniformly distributed two oxides provide abundant and evenly dispersed energy barriers at the dual-oxide interfaces throughout the entire fibril-in-tubes, representing a promising candidate to stabilize metal species.

#### Sintering resistance of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes

As shown in Fig. 3a and S7,† sub-3 nm Pt clusters can be uniformly loaded onto the surfaces of the dual-oxide fibril-intubes via the widely used wet-impregnation approaches for industrial catalysts. The Pt loading density was controlled to be 1 wt%, as confirmed by inductively coupled plasma (ICP) analysis and energy-dispersive X-ray spectroscopy (EDX) spectra presented in Table S1.† To carefully evaluate the thermal stability, the Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes were aged at a series of harsh temperatures in dry and humid air. Generally, if exposed to steam, metal sintering could be accelerated due to the formation of volatile compounds coordinated with water. 19 Based on the ex situ TEM analysis (Fig. 3 and S8†), including the elemental mappings, no observable agglomeration of Pt clusters was visualized after the aging upon 500, 600, and 700 °C in dry air for 2 h, and even at 700 °C in humid air (10 vol% of steam) for 2 h or 750 °C in dry air for 10 h. The XRD patterns of Pt@CeO2/Al2O3 fibril-in-tubes before and after ex situ aging at a series of high temperatures show exclusively reflections of CeO<sub>2</sub> (Fig. S9†). The absence of diffractions indexed to Pt longrange periodicity further confirmed the small size and high dispersity of Pt clusters on these dual-oxide fibril-in-tubes.20 More specifically, the AC-HAADF-STEM images of Pt@CeO<sub>2</sub>/ Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes after aging at 750 °C in dry air for 10 h clearly demonstrated that there is no aggregated Pt cluster or nanoparticle that could be visualized across the substrate (Fig. S10†).

The sintering resistance of Pt clusters on CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> nanofibers with different Ce/Al molar ratios was also investigated. Due to the inherently stronger binding energy between Pt and CeO<sub>2</sub> compared to that with Al<sub>2</sub>O<sub>3</sub>,<sup>21</sup> Pt clusters exhibited significantly enhanced sinter-resistance on CeO<sub>2</sub> nanofibers in comparison to those on Al<sub>2</sub>O<sub>3</sub> nanofibers. As shown in Fig. S11,† Pt clusters maintained their small size on columnar CeO<sub>2</sub> nanofibers after being aged at 700 °C for 2 h, while they underwent further aggregation and increased in diameter to 9.3 nm after aging at 750 °C for 10 h. However, on Al<sub>2</sub>O<sub>3</sub> nanofibers, Pt clusters were observed to grow twice their initial

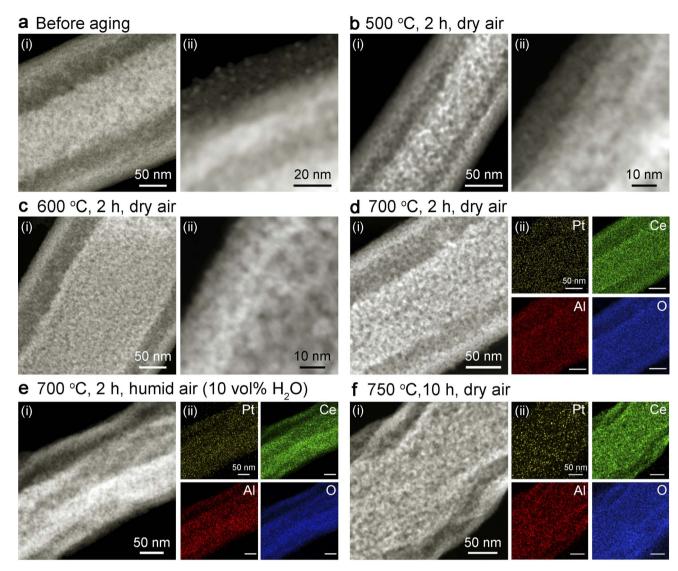


Fig. 3 (a–c) HAADF-STEM images of  $Pt@CeO_2/Al_2O_3$  (a) before and after aging in dry air at (b) 500 and (c) 600 °C for 2 h. (d–f) HAADF-STEM images and elemental mappings of  $Pt@CeO_2/Al_2O_3$  after aging (d) in dry air at 700 °C for 2 h, (e) in humid air (10 vol% of water) at 700 °C for 2 h, and (f) in dry air at 750 °C for 10 h.

size at a relatively low temperature of only 600 °C (Fig. S12†). Dual-oxide supports were endowed with efficiently promoted capability for stabilizing Pt clusters, in comparison with the single-component nanofibers. As shown, Pt clusters slightly grew from 2.3 nm to 4.2 nm on  $\text{CeO}_2/\text{Al}_2\text{O}_3$ -2.5 after being aged at 750 °C in air for 10 h (Fig. S13a and b†). However, when the Ce/Al atomic ratio decreased to 0.8, the loaded 2.3 nm-Pt clusters sintered to reach a size of 4.5 nm after being aged at 750 °C in air for 10 h (Fig. S13c and d†).

In addition to sintering, leaching, which refers to the diffusion of metal into the surrounding environment, poses another threat to the lifespan of the catalyst. Exposure to an oxidative atmosphere can facilitate the oxidation of metallic Pt into more volatile  $PtO_x$ , leading to irreversible metal leaching.<sup>22</sup> Taking advantage of the naturally formed network structure in electrospun nanofibers, the emitted  $PtO_x$  species from Pt clusters located on the outer surface of tubes could be trapped by

neighboring fibril-in-tubes. Moreover, in comparison with the case of Pt clusters supported on conventional  $CeO_2$  nanofibers (Fig. S11†), the retention rate of Pt (determined by ICP) after aging at 700 °C in air for 2 h was increased by the  $CeO_2/Al_2O_3$  fibril-in-tubes from 61.4% to 71.4%. The promoted leaching resistance can be ascribed to the synergistic stabilization by the dual-oxide composition and unique fibril-in-tube nanostructure. In particular, the diffused Pt species can be effectively trapped by the multilayered surfaces as shown in Fig. S14,† therefore contributing to the high dispersion of Pt clusters after harsh aging processes, as demonstrated by the elemental mapping in Fig. 3d–f. These results sufficiently illustrated the elegant all-in-one design of  $CeO_2/Al_2O_3$  fibril-in-tubes, in terms of both the structure and component, for boosting the thermal stability of the whole catalytic system.

As an emerging modern technology to unravel the underlying sintering resistance mechanism, in situ microscopic

observations can provide in-depth information on the dynamic changes of both the metal and support upon aging in different atmospheres.23 To exclude the complex impacts of the atmosphere, we recorded the time-series HAADF-STEM images of Pt@CeO2/Al2O3 at temperatures ranging from room temperature to 900 °C under vacuum, with regard to the thermal stress only (Fig. 4a, S15 and S16†). For quantitatively evaluating the thermal stability, we tracked the size change of Pt clusters

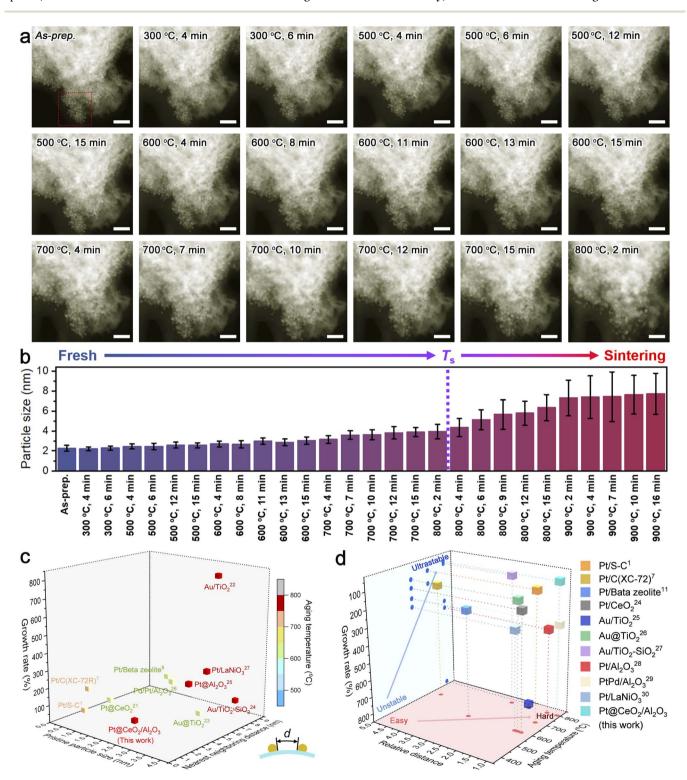


Fig. 4 (a and b) In situ HAADF-STEM observation of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> at elevated temperatures (a) and the corresponding size evolution of Pt clusters (b). The scale bars in (a) indicate 20 nm. The HAADF-STEM images were colored for a better demonstration. (c and d) Ashby chart plotting (c) pristine particle size, nearest neighboring distance versus the growth rate at a certain aging temperature, and the relative distance, (d) the growth rate versus the aging temperature for Pt@CeO2/Al2O3 and other reported sinter-resistant catalyst systems. The inset in (c) illustrates the neighboring distance.

(Fig. S17†) and summarized the results in Fig. 4b. During the harsh aging process, no observable sintering was visualized. The Pt clusters with an initial average diameter of merely 2.3 nm kept a size smaller than twice their initial size and sat on the support individually in ultra-close proximity, until being exposed at 800 °C for 2 min, strongly suggesting the superb sinter-resistance. After considering the desirable diameters in the range of industrial catalysts (that is 1.5–4.0 nm),<sup>7</sup> the limit of sinter-resistance of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> can be roughly regarded as 800 °C (denoted as  $T_s$  as highlighted in Fig. 4b).

To date, there is rarely a reported method for impartially quantifying the anti-sintering capability in diverse systems. By taking the minimum value of the distance between one cluster and any neighboring cluster (illustrated in the inset of Fig. 4c and S18†), the intrinsic dispersity of metal species on their supports can be carefully studied. On  $CeO_2/Al_2O_3$  fibril-in-tubes, the average nearest neighboring distance of Pt clusters could be measured to be only around 2.1 nm, which is shorter than the pristine diameter of one Pt cluster. Such an ultra-close distribution causes a great challenge for stabilizing Pt clusters, as discussed above.

For a synthetic comparison, we summarized the pristine size, the average nearest neighboring distance, and the growth rate at a certain aging temperature of several recently reported sinter-resistant catalyst systems with different well-designed compositions and structures in Fig. 4c.1,7,11,24-30 The growth rate of the metal species is defined as the difference between the diameter after growth and the initial diameter as a percentage of the initial diameter. All the involved systems were based on metal catalysts with pristine sizes similar to the Pt clusters used in this work. Moreover, we correlated the average nearest neighboring distance with the pristine particle size (defined as relative distance) and plotted it versus the aging temperature and growth rate (Fig. 4d). As shown, although the Pt clusters on the CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes were in ultra-close proximity with the average nearest neighboring distance of merely 0.93 of the pristine particle diameter, the catalytic system can maintain a small growth rate below 100% at 800 °C for a while. The boosted sintering resistance of Pt clusters can be largely attributed to the all-in-one stabilizing effects of the CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes as illustrated in Fig. 1: (i) the built-in energy barriers energetically stabilized these Pt clusters; (ii) the pores and channels physically impeded the migration of Pt; and (iii) the promoted adhesion between the metal and support chemically anchored Pt.

To shed light on how the whole system failed eventually, the *in situ* heating temperature was further elevated (Fig. S16†). It is worth mentioning that the sintered Pt nanoparticles maintained a well-crystallized structure at temperatures up to 900 °C, which is somewhat higher than its melting point (727 °C, for 3 nm-Pt).³ However, the nanofibrous support was subjected to reconstruction during heating over 800 °C, in terms of the densification and the emergence of voids and cracks. Once the support suffered from reconstruction, the metal sintering would be severely accelerated, mainly because of the significantly shortened neighboring distance. Therefore, the *in situ* HAADF-STEM observation revealed that promoting the thermal

stability of support has a profound impact on boosting the sinter-resistance of the catalytic systems, and should be highly addressed for the future design of durable catalysts with high metal loading.

According to the X-ray photoelectron spectroscopy (XPS) results (Fig. S19a†), the binding energies of Ce<sup>3+</sup> and Ce<sup>4+</sup> shifted to lower positions by 0.2-0.5 eV after being aged at high temperatures in air. The atomic ratio of Ce<sup>3+</sup> to Ce<sup>4+</sup> declined accordingly. No obvious chemical shift of Al 2s spectra was visualized (Fig. S19b†). The Pt 4d spectra exhibited an increased proportion of positively charged platinum species ( $Pt^{\delta+}$ ) after aging at high temperatures, along with corresponding shifts towards higher binding energy (Fig. S19c†). This observation suggests a more pronounced interfacial charge transfer from Pt to the support at the interface. Moreover, the peak assigned to the lattice oxygen in Ce<sub>2</sub>O<sub>3</sub> and CeO<sub>2</sub> shifted to higher binding energies (Fig. S19d†), which could be ascribed to the generation of oxygen vacancies (O<sub>v</sub>). The gradually increased indicator value of g peaks at 2.003 in the electron paramagnetic resonance (EPR) spectra (Fig. S19e†) further confirmed the enriched oxygen vacancies during heat treatment in an oxidative atmosphere.

In principle, the number of O<sub>v</sub> is proportional to the concentration of Ce3+, where one oxygen defect can be generated accompanied by the formation of two Ce<sup>3+</sup> ions.<sup>32</sup> The exceptional increase of Ov in Pt@CeO2/Al2O3 should be largely ascribed to the incorporation of metal species into CeO2, including both  $Pt^{\delta+}$  and  $Al^{3+}$ . Consequently, the abundant oxygen vacancies provide ample anchoring sites for stabilizing Pt species, namely Pt-O<sub>v</sub>-Ce sites, by improving the adhesion between Pt and CeO<sub>2</sub>.31 Moreover, the abundant Pt-O<sub>v</sub>-Ce sites are supposed to be present not only within CeO<sub>2</sub> nanodomains but also at dual-oxide interfaces and even in Al2O3 nanodomains as well, by considering the doping of Ce atoms into Al<sub>2</sub>O<sub>3</sub> as we discussed above. Therefore, ultra-close Pt clusters with a size below 3 nm could be carefully stabilized against sintering on CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes, becoming a promising catalyst for high-temperature reactions.

#### 3.3 Catalytic soot combustion performance

Diesel particulate, consisting mainly of carbon nanoparticles with 20 nm in size, has seriously threatened public health in recent decades.<sup>33</sup> To address this issue, employing efficient catalysts to remove the diesel particles from the source and further reduce the combustion temperature is extremely urgent. As shown in Fig. 5a, the naturally overlapped fibril-in-tubes with open channels can effectively trap the diesel particulates and thereby significantly promote the catalyst–diesel contact efficiency. On a more specific scale (Fig. 5b), the abundant oxygen vacancies at the metal/support interfaces can favor the activation of gaseous oxygen and the migration of active oxygen species to the surface, and thus promote the reaction thermodynamics significantly.<sup>34</sup>

To evaluate the catalytic performance, diesel combustion with a temperature-programmed oxidation method was conducted in a loose contact mode, which is the main fashion under practical conditions.<sup>35</sup> The soot conversion curves over the Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub>

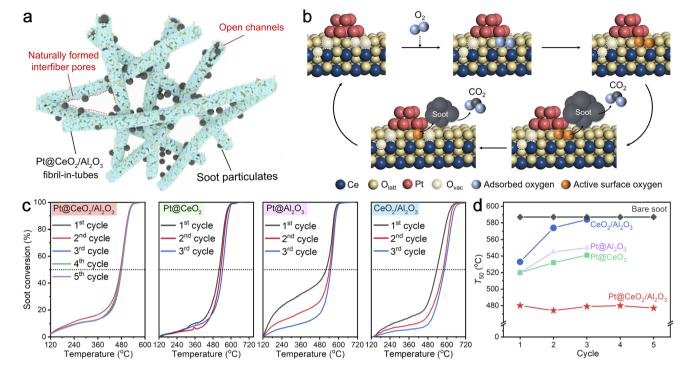


Fig. 5 (a) Schematic illustration of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes physically trapping diesel soot. (b) Activation pathways for O<sub>2</sub> at the Pt/CeO<sub>2</sub> interface. Note that these structures are provided for illustration but are not calculated structures. (c) Soot conversion over  $Pt@CeO_2/Al_2O_3$  fibrilin-tubes, Pt@CeO<sub>2</sub> nanofibers, Pt@Al<sub>2</sub>O<sub>3</sub> nanofibers, and bare CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes without Pt. (d)  $T_{50}$  of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> within 5 cycles and Pt@CeO2 nanofibers, Pt@Al2O3 nanofibers, and CeO2/Al2O3 fibril-in-tubes within 3 cycles.

fibril-in-tubes, Pt@CeO2 nanofibers, Pt@Al2O3 nanofibers, and the bare CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes without Pt for several cycles are shown in Fig. 5c. The catalytic activity was quantitatively evaluated from the values of  $T_{10}$ ,  $T_{50}$ , and  $T_{90}$ , which were defined as the temperatures at 10%, 50%, and 90% of soot conversion, respectively. Compared with the soot particles without any catalyst (Fig. S20,†  $T_{10}$ ,  $T_{50}$ , and  $T_{90}$  of 501, 587, and 672 °C, respectively), the presence of CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes alone can decrease the  $T_{10}$ ,  $T_{50}$ , and  $T_{90}$  to 258, 533, and 607 °C at its first reaction cycle. After being loaded with only 0.8 wt% of Pt clusters, the Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes effectively lowered the  $T_{10}$ ,  $T_{50}$ , and T<sub>90</sub> to 247, 480, and 518 °C further, being superb compared to Pt@CeO<sub>2</sub> nanofibers and Pt@Al<sub>2</sub>O<sub>3</sub> nanofibers. In particular, the ignition temperature (i.e.,  $T_{10}$ ) of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> was 254 °C lower than that of the reaction without catalysts. Such a low soot conversion temperature at a relatively high ramping rate of 10 °C min<sup>-1</sup> is competitive with many recently reported catalyst systems (Table S2†).36-40

More specifically, the catalytic performance of Pt@CeO<sub>2</sub>/  $Al_2O_3$  fibril-in-tubes, especially the  $T_{50}$ , did not decline during five consecutive rounds of high-temperature and exothermic reactions but instead showed a stable and slightly fluctuating trend (summarized in Fig. 5d). The HAADF-STEM images of Pt@CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes after each cycle of soot combustion are summarized in Fig. S21.† Despite the exothermic nature of the reaction ( $\Delta H = -393.5 \text{ kJ mol}^{-1}$ ), which leads to a localized increase in temperature around the active sites, specifically at the Pt/CeO2 interface, both the support and Pt

clusters demonstrate exceptional thermal stability. However, the catalytic performances of bare CeO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes, Pt@CeO<sub>2</sub> nanofibers, and Pt@Al<sub>2</sub>O<sub>3</sub> nanofibers were reduced somehow. As shown, the loaded Pt clusters sintered significantly to 12.1 nm on the CeO<sub>2</sub> nanofibers and 17.6 nm on the Al<sub>2</sub>O<sub>3</sub> nanofibers after 3 cycles of diesel combustion (Fig. S22†). Therefore, these observations unequivocally demonstrate the exceptional sinter-resistance of Pt@CeO2/Al2O3 fibril-in-tubes under reaction conditions, which presents a significantly greater challenge than merely stabilizing metal species against thermal stress.

#### Conclusions 4

In summary, we have demonstrated all-in-one designed CeO<sub>2</sub>/ Al<sub>2</sub>O<sub>3</sub> fibril-in-tubes to boost the sinter-resistance of supported 2.3 nm Pt clusters in ultra-close proximity. The strong support, CeO2, effectively immobilizes Pt clusters with strong adhesion, and the adjacent weak support, Al<sub>2</sub>O<sub>3</sub>, with low adhesion, constructs energy barriers to impede the migration of Pt species across the entire substrate. Moreover, the hierarchical pores and channels physically confine the Pt clusters. Therefore, the sinter-resistance of these 2.3 nm Pt clusters can be boosted to over 750 °C, under an oxidative and even steam-containing atmosphere. The in situ HAADF-STEM observation revealed that significant sintering of Pt clusters started at 800 °C, coinciding with the reconstruction of the supports. In diesel combustion, the Pt@CeO2/Al2O3 fibril-in-tubes decreased the ignition temperature by about 254 °C and showed reliable stability within 5 cycles. This work represents a rational design of sinter-resistant catalytic systems with high activity and durability by integrating multiple advances into one.

# Data availability

The data supporting this article have been included as part of the ESI.†

### **Author contributions**

Wanlin Fu: investigation, writing, data analysis; Kuibo Yin: methodology, data analysis, supervision; Zhihui Li: investigation, writing; Jun Wang: investigation; Mingyu Tang: investigation; Jilan Tian: investigation; Litao Sun: supervision, project administration; Yueming Sun: supervision, project administration; Yunqian Dai: supervision, project administration, conceptualization, funding acquisition.

## Conflicts of interest

The authors declare no competing interests.

# Acknowledgements

This work was financially supported by the National Key Research and Development Program of China (2022YFA1505700), the National Natural Science Foundation of China (22475044, 21975042 and 12174050), Pre-Research Fund of Ministry of Education of China (No. 8091B022212), the Project of Qinglan Talent of Jiangsu, and the Priority Academic Program Development of Jiangsu Higher Education Institutions.

## References

- C. L. Yang, L. N. Wang, P. Yin, J. Liu, M. X. Chen, Q. Q. Yan,
   Z. S. Wang, S. L. Xu, S. Q. Chu, C. Cui, H. Ju, J. Zhu, Y. Lin,
   J. Shui and H. W. Liang, *Science*, 2021, 374, 459–464.
- 2 R. Jin, G. Li, S. Sharma, Y. Li and X. Du, *Chem. Rev.*, 2021, 121, 567–648.
- 3 Y. Dai, P. Lu, Z. Cao, C. Campbell and Y. Xia, *Chem. Soc. Rev.*, 2018, 47, 4314–4331.
- 4 E. Toulkeridou, J. Kioseoglou and P. Grammatikopoulos, *Nanoscale Adv.*, 2022, **4**, 4819–4828.
- J. A. Rodriguez, D. C. Grinter, Z. Liu, R. M. Palomino and S. D. Senanayake, *Chem. Soc. Rev.*, 2017, 46, 1824–1841.
- 6 S. Hu and W. X. Li, Science, 2021, 374, 1360-1365.
- 7 P. Yin, S. Hu, K. Qian, Z. Wei, L. Zhang, Y. Lin, W. Huang, H. Xiong and W. Li, *Nat. Commun.*, 2021, **12**, 4865.
- 8 Y. Zhang, J. Zhang, B. Zhang, R. Si, B. Han, F. Hong, Y. Niu, L. Sun, L. Li, B. Qiao, K. Sun, J. Huang and M. Haruta, *Nat. Commun.*, 2020, **11**, 558.
- 9 L. Shang, T. Bian, B. Zhang, D. Zhang, L. Wu, C. Tung, Y. Yin and T. Zhang, *Angew. Chem., Int. Ed.*, 2014, 53, 250–254.

- 10 Z. Yang, X. Xie, G. Peng, L. Shang and T. Zhang, Acc. Mater. Res., 2024, 5, 194–205.
- 11 J. Zhang, L. Wang, B. Zhang, H. Zhao, U. Kolb, Y. Zhu, L. Liu, Y. Han, G. Wang, C. Wang, D. S. Su, B. C. Gates and F. S. Xiao, *Nat. Catal.*, 2018, 1, 540–546.
- 12 A. L. A. Marinho, R. C. Rabelo-Neto, F. Epron, N. Bion, F. S. Toniolo and F. B. Noronha, *Appl. Catal.*, B, 2020, 268, 118387.
- 13 J. Zhou, G. Xiang, T. Zhai, Z. Liu, W. Zhao, X. Liang and L. Wang, *Nat. Commun.*, 2022, **13**, 327.
- 14 H. Chen, W. Lin, Z. Zhang, Z. Yang, K. Jie, J. Fu, S. Yang and S. Dai, *Chem. Sci.*, 2020, **11**, 5766–5771.
- 15 A. M. Gänzler, M. Casapu, F. Maurer, H. Störmer, D. Gerthsen, G. Ferré, P. Vernoux, B. Bornmann, R. Frahm, V. Murzin, M. Nachtegaal, M. Votsmeier and J. D. Grunwaldt, ACS Catal., 2018, 8, 4800–4811.
- 16 J. Lee, S. Kang, E. Lee, M. Kang, J. Sung, T. J. Kim, P. Christopher, J. Park and D. H. Kim, *J. Mater. Chem. A*, 2022, **10**, 7029–7035.
- 17 Y. Liu, A. J. McCue, P. Yang, Y. He, L. Zheng, X. Cao, Y. Man, J. Feng, J. A. Anderson and D. Li, *Chem. Sci.*, 2019, **10**, 3556–3566.
- 18 W. Fu, W. Xu, K. Yin, X. Meng, Y. Wen, L. Peng, M. Tang, L. Sun, Y. Sun and Y. Dai, *Mater. Horiz.*, 2023, **10**, 65.
- 19 H. Xiong, D. Kunwar, D. Jiang, C. E. G. Vargas, H. L. C. Du, G. Canning, X. I. P. Hernandes, Q. Wan, S. Lin, S. C. Purdy, J. T. Miller, K. Leung, S. S. Chou, H. H. Brongersma, R. Veen, J. Huang, H. Guo, Y. Wang and A. K. Datye, *Nat. Catal.*, 2021, 4, 830–839.
- 20 C. Wang, S. Mao, Z. Wang, Y. Chen, W. Yuan, Y. Ou, H. Zhang, Y. Gong, Y. Wang, B. Mei, Z. Jiang and Y. Wang, *Chem*, 2020, 6, 752–765.
- 21 N. J. O' Connor, A. S. M. Jonayat, M. J. Janik and T. P. Senftle, *Nat. Catal.*, 2018, **1**, 531–539.
- 22 J. Jones, H. Xiong, A. T. DeLaRiva, E. J. Peterson, H. Pham, S. R. Challa, G. Qi, S. Oh, M. H. Wiebenga, X. I. P. Hernández, Y. Wang and A. K. Datye, *Science*, 2016, 353, 150-154.
- 23 Z. Chen, H. Cheng, Z. Cao, J. Zhu, T. Blum, Q. Zhang, M. Chi and Y. Xia, *Nano Lett.*, 2024, 24, 1392–1398.
- 24 J. S. Du, T. Bian, J. Yu, Y. Jiang, X. Wang, Y. Yan, Y. Jiang,C. Jin, H. Zhang and D. Yang, *Adv. Sci.*, 2017, 4, 1700056.
- 25 H. Tang, F. Liu, J. Wei, B. Qiao, K. Zhao, Y. Su, C. Jin, L. Li, J. Liu, J. Wang and T. Zhang, *Angew. Chem., Int. Ed.*, 2016, 5, 10606–10611.
- 26 S. Liu, W. Xu, Y. Niu, B. Zhang, L. Zheng, W. Liu and J. Wang, Nat. Commun., 2019, 10, 5790.
- 27 Y. Zhang, J. Zhang, B. Zhang, R. Si, B. Han, F. Hong, Y. Niu, L. Sun, L. Li, B. Qiao, K. Sun, J. Huang and M. Haruta, *Nat. Commun.*, 2020, 11, 558.
- 28 A. Aitbekova, C. Zhou, M. L. Stone, J. S. Lezama-Pacheco, A. C. Yang, A. S. Hoffman, E. D. Goodman, P. Huber, J. F. Stebbins, K. C. Bustillo, P. Ercius, J. Ciston, S. R. Bare, P. N. Plessow and M. Cargnello, *Nat. Mater.*, 2022, 21, 1290–1297.

29 J. Oh, A. Beck, E. D. Goodman, L. T. Roling, A. Boucly, L. Artiglia, F. Abild-Pedersen, J. A. Bokhoven and M. Cargnello, *ACS Catal.*, 2023, **13**, 1812–1822.

**Edge Article** 

- 30 S. Zhang, W. Zhou, J. Mao, K. An, N. Li, T. Qin, L. Chen, X. Liu, B. Mei, Z. Jiang, Z. Wang, Y. Yamauchi and Y. Liu, J. Mater. Chem. A, 2022, 10, 8227–8237.
- 31 J. Yu, X. Qin, Y. Yang, M. Lv, P. Yin, L. Wang, Z. Ren, B. Song, Q. Li, L. Zheng, S. Hong, X. Xing, D. Ma, M. Wei and X. Duan, J. Am. Chem. Soc., 2024, 146, 1071–1080.
- 32 S. Pollitt, V. Truttmann, T. Haunold, C. Garcia, W. Olszewski, J. Llorca, N. Barrabés and G. Rupprechter, *ACS Catal.*, 2020, **10**, 6144–6148.
- 33 X. Mei, X. Zhu, Y. Zhang, Z. Zhang, Z. Zhong, Y. Xin and J. Zhang, *Nat. Catal.*, 2021, 4, 1002–1011.
- 34 L. Nie, D. Mei, H. Xiong, B. Peng, Z. Ren, X. I. P. Hernandez, A. DeLaRiva, M. Wang, M. H. Engelhard, L. Kovarik, A. K. Datye and Y. Wang, *Science*, 2017, 358, 1419–1423.

- 35 Y. Li, T. Qin, Y. Wei, J. Xiong, P. Zhang, K. Lai, H. Chi, X. Liu, L. Chen, X. Yu, Z. Zhao, L. Li and J. Liu, *Nat. Commun.*, 2023, 14, 7149.
- 36 M. J. Kim, G. H. Han, S. H. Lee, H. W. Jung, J. W. Choung, C. H. Kim and K. Y. Lee, J. Hazard. Mater., 2020, 384, 121341.
- 37 Y. Chen, G. Shen, Y. Lang, R. Chen, L. Jia, J. Yue, M. Shen, C. Du and B. Shan, *J. Catal.*, 2020, 84, 96–105.
- 38 J. H. Lee, S. H. Lee, J. W. Choung, C. H. Kim and K. Y. Lee, *Appl. Catal.*, *B*, 2019, **246**, 356–366.
- 39 N. S. Portillo-Vélez and R. Zanella, Chem. Eng. J., 2020, 385, 123848.
- 40 W. Ren, T. Ding, Y. Yang, L. Xing, Q. Cheng, D. Zhao, Z. Zhang, Q. Li, J. Zhang, L. Zheng, Z. Jiang and X. Li, ACS Catal., 2019, 9, 8772–8784.