

Cite this: *J. Mater. Chem. A*, 2024, 12, 31557

A ciprofloxacin derived task specific ionic liquid as a highly selective extractant of thorium *versus* uranium†‡

David Lledó,^a Guillermo Grindlay,^b H. Q. Nimal Gunaratne,^c Abel de Cózar,^{d,e} Ana Sirvent^f and José M. Sansano^{*f}

A selective extraction system of thorium(IV), formed with a TSIL derived from ciprofloxacin and [BMIM][NTf₂] as a co-solvent, is described. Under acidic conditions, this IL solution was able to complex selectively this metal *versus* the rest of the other metals of the periodic table. The synthesis of the TSIL was detailed using known procedures and it was isolated in good overall yield. The extraction coefficients (K) were determined by a microextractive survey at 25 °C. Spectroscopic analyses of thorium(IV) and uranium(VI) complexes were performed in order to demonstrate the strength of the metal–TSIL interaction, which was supported by DFT-based computational optimization of the formation of the experimentally observed complexes. Kinetic analysis, loading tests for the extractive protocol, and the optimization for recycling were also performed to justify the conditions of a laboratory prototype for this selective extraction of thorium(IV) salts.

Received 12th September 2024
Accepted 22nd October 2024

DOI: 10.1039/d4ta06496h

rsc.li/materials-a

Introduction

Stimulated by the world's demand for energy, nuclear reactors are expected to play a key role as a power source in the future due to the low emission of carbon dioxide or other greenhouse gases and the abundant fuel reservoirs.^{1,2} However, regarding the fuel sources, uranium and thorium (the actinide elements that are predominantly present in nature) are very dispersed in ores and require selective extraction methods. Additionally, the waste that is generated as a result of the use of this energy source poses a great threat to the environment and human health. In this regard, one of the most important processes in

the management of nuclear waste is the intra- and inter-group separation of lanthanides and actinides.

Thorium is rather diluted in rock thus requiring more mining, milling and treatment local to where it is recovered than is the case for uranium.³ Apparently, thorium is much more abundant than uranium in nature³ and has become one of the important potential energy sources for the future. In fact, thorium is occasionally heralded as a 'safe' alternative to uranium and plutonium and it has often been integrated into reactor system designs *via* accelerator-driven systems.⁴ This is because a thorium-232 (²³²Th) nucleus has the ability to produce a uranium-233 (²³³U) nucleus by absorbing a neutron. Thorium itself is known as fertile⁵ because it is not fissile but provides a fissile uranium isotope ²³³U. In the long term, consumption of thorium could increase substantially if its use as a nuclear fuel becomes commercialized. Thorium is anticipated to produce lower quantities of minor actinides and no plutonium, considerations often perceived as key advantages in terms of long-term radioactive waste management.

In addition, [Th(IV)] and its compounds are highly toxic and cause severe damage to bone and kidney through very long-term exposures. Conventional methods of Th(IV) detection are complicated and costly. However, the daughters of Th-229 (Ac-225 and Bi-213) and other α -emitting radioisotopes are rapidly becoming of great interest for short-range and site-specific therapy of cancers and micrometastatic diseases.⁶

The separation of thorium(IV) is very important in countries such as India and China. However, the process is quite challenging and co-extraction of uranium and thorium is frequently reported.^{7–11}

^aMedalchemy, S. L. Ancha de Castelar, 46-48, entlo. A. San Vicente del Raspeig, 03690-Alicante, Spain

^bDepartment of Analytical Chemistry, Nutrition and Food Sciences, University of Alicante, PO Box 99, 03080 Alicante, Spain

^cThe QUILL Research Centre, School of Chemistry and Chemical Engineering, The Queen's University of Belfast, Stranmillis Road, Belfast, Northern Ireland, BT9 5AG, UK

^dDepartamento de Química Orgánica I/Kimika Organikoa I Saila, Facultad de Química/Kimika Fakultatea, Universidad del País Vasco/Euskal Herriko Unibertsitatea (UPV/EHU), Donostia International Physics Center (DIPC), Centro de Innovación en Química Avanzada (ORFEO-CINQA), P. K, 1072, 20018 San Sebastián-Donostia, Spain

^eIkerbasque, Basque Foundation for Science, Plaza Euskadi 5, 48009, Bilbao, Spain

^fDepartamento de Química Orgánica, Centro de Innovación en Química Avanzada (ORFEO-CINQA), Institute of Organic Synthesis, Universidad de Alicante, Ctra. Alicante-San Vicente s/n, 03080-Alicante, Spain. E-mail: jmsansano@ua.es

† Dedicated to Professors Carmen Nájera and Miguel Yus for their outstanding contribution to Organic and Organometallic Chemistry.

‡ Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ta06496h>



For this purpose, the most common traditional methods are liquid–liquid extraction, ion exchange high performance liquid chromatography¹² and the use of hollow fiber renewal liquid membranes (HFRLM, designed for reusing the system).^{13–16} However, a significant disadvantage of these processes is the waste chemicals generated.¹⁷

Examples of liquid–liquid extraction for specific and selective Th(IV) separation have been described in the literature using as extraction systems, for instance, phosphate buffer solutions,¹⁸ hydrophobic deep eutectic solvents using thorin as a chelating agent,¹⁹ or fatty acids.²⁰ Separation processes that employ extractant systems based on 2-[4-(2,4,4-trimethylpentan-2-yl)phenoxy] acetic acid (POAA),²¹ functionalized graphene oxide with phenanthroline diamide (GO-PDA),²² or 1,5-bis[*o*-(dioxiphosphoryl)- π -ethylphenoxy]-3-oxapentane and tri-octylamine have been also used to selectively recover Th(IV) from solutions.^{23,24} Other ligands that have been found to be specific for the selective extraction of thorium(IV) are *N*-*n*-heptylaniline,^{25,26} 2,3-dihydroxynaphthalene,²⁷ tri-*n*-butylphosphate (TBP),²⁸ *N,N*-di-*n*-hexyloctanamide (DHOA),²⁹ tri-*n*-octylphosphineoxide (Cyanex 923)³⁰ and bis(2,4,4-trimethyl)pentyl phosphinic acid (Cyanex 272)³¹ were found to be specific Th(IV) ligands for extractive processes.^{32,33} Selective extraction of thorium from uranium and rare earth elements using a sulfonated covalent organic framework and its membrane derivate was also reported.³⁴ Metal organic frameworks (MOFs) have been employed as selective extractants.³⁵

If we focus our attention on the favorable properties of ionic liquids (ILs) as extractants,^{36–38} room temperature ionic liquids (RTILs) are considered as a replacement of molecular diluents in the extraction of metal ions from an aqueous phase. Thus, for example, dialkylsulfosuccinate-based ionic-liquids,³⁹ and *N,N*-dialkyl-malonamic acid (MA)-based ionic liquid anions were synthesized and applied for the extraction of thorium ions using a nitric acid solution. The solid samples were obtained by simultaneous extraction and solidification of Th(IV) based on a self-assembly process. Dioctadecyldimethylammonium ([DC DMA]) was pioneered as the preferred organic cation of the ionic liquids for the extraction process.^{40,41} IL based solvent systems are found to be radio resistant compared to molecular diluent based solvent systems. They act as a sink for the radiation damage to protect the ligand functionality. Along these lines, TSILs have been used for selective extraction of uranium (phosphoramidate-containing ILs)⁴² and for excellent separation of thorium(IV) from other metals (including uranium);⁴³ a TSIL formed by CMPO-functionalized ionic liquid 1-[3-[[[diphenylphosphinyl]acetyl]amino]propyl]-3-tetradecyl-1*H*-imidazol-3-ium hexafluorophosphate (CMPO-FIL) was used for general Ln(III), Th(IV) and U(VI) extraction.⁴⁴ TSILs are frequently used for the extraction of other actinides.⁴⁵

In general, stripping procedures are performed employing inorganic acids at different pHs. In most cases, the recovery of the TSIL is not considered but only the amount of actinide ion stripped. Employing ILs together with extractive ligands is very well documented, for example amines,⁴⁶ 1,3-diketones (stripping with SC-CO₂),⁴⁷ *N,N*-dialkylamides (stripping with SC-CO₂),⁴⁸ diglycolamides,^{49–51} phosphine oxides (stripping with

oxalic acid),⁵² using phosphane derived ligands (stripping with acidic solutions),⁵³ methyl imidazoles,^{54,55} *N,N'*-dimethyl-*N,N'*-dioctyl-4-oxaheptanediamide (DMDOHA),⁵⁶ carbamoylmethylphosphine oxides (CMPO),^{57,58} polymeric CMPO,⁵⁹ *N,N,N,N*-tetraoctyldiglycolamide (TODGA),⁶⁰ other tridentate and tetradentate amides,⁶¹ and *N,N*-di(2-ethylhexyl)-diglycolamic acid.⁶² In most cases, the ionic liquid based systems stripping was found to be the most challenging compared to molecular diluents and required strong aqueous complexing agents.

Concerning the coordination of thorium(IV) and uranium(VI) (uranyl cation in aqueous solution) the hexacoordination is the most common feature,^{63,64} although there are uncommon environments published in the literature.^{65,66} In addition, one of the most promising areas in f-element research in ILs is computer-aided simulations that aim to elucidate the solvating power of ILs towards actinides, lanthanides, and even fission products, all of which are important components of nuclear wastes and processing streams.⁶⁷


According to all these precedents, we envisage that the design and computational simulation of a TSIL considering the preferential coordination of Th(IV) would be crucial for efficient modulation of the selectivity of separation of this metal and for the implementation of a very easy and environmentally benign method for the recovery of the metal and the TSIL/IL system.⁶⁸ Herein, we report a concise synthesis of a TSIL system based on antibiotic ciprofloxacin for highly selective extraction of thorium(IV).

Results and discussion

Synthesis of the TSIL 4 and preliminary microextractions

1,3-Dicarbonyl compounds are known as excellent ligands for stabilizing metal complexes,⁶⁹ specially in the case of highly coordinative rare earth metals.⁷⁰ Previous results demonstrated that an IL tethered to a 1,2-diamide motif exhibited a potent donor effect extracting all lanthanide series without any selectivity.⁶² The basic and rapid *in silico* analysis of the electronic structure/interactions of the β -dicarbonylic moiety, combining an aromatic ketone and an amido array (in order to modulate the affinity by the cationic metals) and including a hydrophobic area, able to interact with the solvent of the extractive system, turned our attention to the ciprofloxacin structure **1**. The inexpensive commercially available compound **1** was *N*-alkylated with ethyl bromide, in an acetonitrile/water mixture, and catalyzed by potassium iodide. The resulting compound **2** (isolated in 92% yield) underwent the amidation reaction using *N,N*-diethylamine, after the *in situ* generation of the chloride of the corresponding acid with thionyl chloride in dichloromethane, at 0 °C for 30 min. Amide **3** (obtained in 95% yield) was transformed on its quaternary ammonium salt, in the presence of *n*-butyl iodide, followed by ion exchange using lithium bis(trifluorosulfonyl)amide in dichloromethane at room temperature for 8 h. These two steps afforded the final TSIL molecule **4** in 89% (78% overall yield from ciprofloxacin **1**) (Scheme 1). It is remarkable that the association of the bis-triflimide anion (NTf₂) would ameliorate the extraction of such metals from an aqueous phase to a hydrophobic environment.



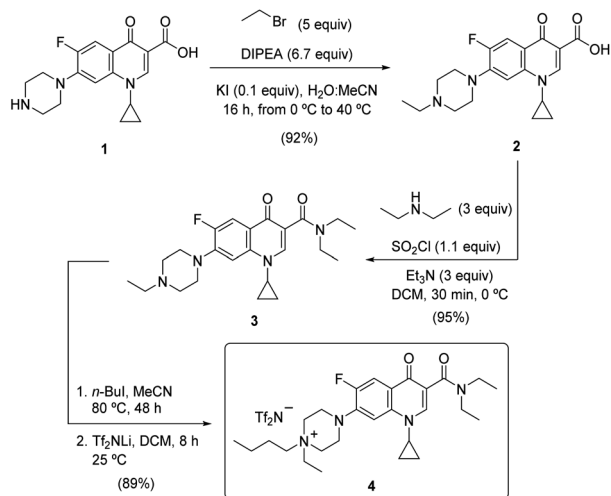

Scheme 1 Synthesis of the TSIL 4.

Next, the micro-extractive multimetallic survey of the extraction system, composed of a 0.005 M solution of TSIL 4 in [BMIM][NTf₂] (100 μL), was performed (at 25 °C) from a multi-metal sample (5 mL) (Li, B, Al, Ti, V, Cr, Mn, Fe, Co, Ni, Cu, Zn, Ga, As, Se, Zr, Mo, Ru, Pd, Ag, Cd, In, Sn, Sb, Te, Pt, Au, Hg, Tl, Pb and Bi) using ICP-MS as an instrumental analytical technique (employing rhodium as an internal standard). For all the elements, the extraction coefficient, defined as the ratio between the concentration of the metal in the organic phase and the aqueous phase after the extraction procedure (eqn (1)), was calculated at different pHs (1–6).

$$K = \text{final } [M]_{\text{org}} / \text{final } [M]_{\text{aq}} \quad (1)$$

Table 1 shows the results obtained under optimum experimental conditions for each element (K_{max}). After analysing the pH range 1–6, in the third column of Table 1 the pHs in which the maximum K was obtained using the ICP technique are depicted. The same conditions were used for the extraction of all elements of Table 1, where K values registered at pH = 1 were also included (fourth column of Table 1) in order to compare the extraction of all metals. With the later value, it was observed that thorium (Table 1, entry 1) was selectively extracted in comparison with other different rare earth metals, and with the rest of the series s, d and p metals (Table 1). Only scandium, mercury and bismuth exhibited a significant (but low) extraction coefficient (K) at the end of the process (Table 1, entries 3, 46 and 49). But the paramount result (and the main goal) of this work was the large extraction difference observed between thorium and uranium (Table 1, entries 1 and 12).

The amazing selectivity of the extraction of thorium(IV) versus uranyl cations or even the rest of rare earth metals controlling the pH at 1 can be observed in the histogram depicted in Fig. 1. Thorium exists as a Th⁴⁺ cation, whereas uranium remains in acidic solutions as the UO₂²⁺ cation, so these cations are chemically very different and consequently, no parallelism is established in the next tests. We will lay emphasis in

Table 1 Extraction coefficients K determined in the microextractive survey at 25 °C

Entry	Metal	pH/ K_{max}	K at pH = 1
1	Th	1/197	197
2	Nd	4/136	8
3	Sc	2/129	30
4	Sm	6/82	3
5	Eu	6/77	3
6	Tb	6/59	3
7	Gd	6/52	1
8	Pr	6/50	4
9	Dy	6/50	2
10	Ho	6/38	3
11	Ce	6/37	0
12	U	6/34	7
13	Er	6/30	1
14	Tm	6/26	1
15	Y	4/25	2
16	Yb	6/21	1
17	La	6/20	0
18	Lu	6/18	2
19	Li	6/2	0
20	B	6/2	0
21	Al	6/8	0
22	Ti	6/107	3
23	V	6/4	1
24	Cr	6/4	0
25	Mn	6/2	0
26	Fe	6/4	1
27	Co	6/1	0
28	Ni	6/1	0
29	Cu	6/21	0
30	Zn	6/32	0
31	Ga	6/8	1
32	As	6/3	0
33	Se	6/0	0
34	Zr	1/3	3
35	Mo	1/2	2
36	Ru	6/4	0
37	Pd	1/4	4
38	Ag	1/6	6
39	Cd	6/4	0
40	In	1/4	4
41	Sn	6/4	0
42	Sb	6/1	0
43	Te	6/3	0
44	Pt	6/0	0
45	Au	6/0	0
46	Hg	1/23	23
47	Tl	6/0	0
48	Pb	6/3	0
49	Bi	2/28	10

demonstrating the high selectivity observed during the extraction process of these two cations.

Spectroscopic analyses of thorium(IV) and uranium(IV) complexes

The metal-cation complexation to the ionic liquid 4 was studied by spectroscopic methods (¹H NMR, ¹³C NMR and FTIR) under analogous conditions. The maximum coordination number of the TSIL (4) ligands per cation was determined by the signal



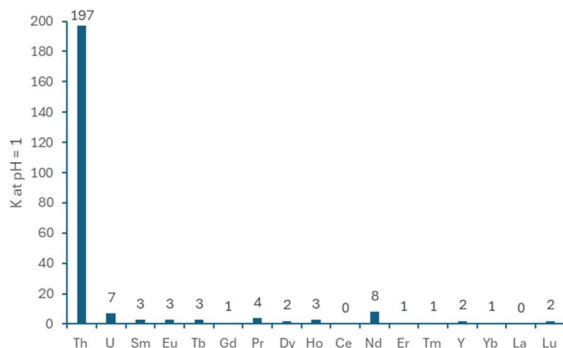


Fig. 1 Plot of the K values at $\text{pH} = 1$ of the extraction of rare earth metals by TSIL 4 in $[\text{BMIM}][\text{NTf}_2]$.

chemical shifting of the singlet that appeared at 7.95 ppm and the doublet located at 7.73 ppm. The additional doublet at 7.42 ppm was hardly affected by the ligand–metal cation interaction. Thus, uranyl nitrate was combined with different proportions of ligand 4 in $\text{DMSO}-d_6$ at room temperature. Although the chemical shift variation was not notable, the sequence of the spectra clearly revealed that the 1 : 1 ratio of uranyl nitrate : TSIL 4 is the coordination pattern in this system (stack plot of Fig. 2A). The difference of ppm in ^{13}C NMR was 0.6 ppm for the two carbonyl groups of the ciprofloxacin scaffold (Fig. 2B). However, a stronger interaction between the thorium(IV) cation and TSIL 4 was observed in DMSO. The increment of the chemical shifts was very important and a 1 : 3 ratio of thorium(IV) nitrate was the coordination pattern (stack plot of Fig. 2C). The separation of the carbonyl group signals between the free ligand 4 and $\text{Th}(\text{IV}) \cdot 4_3$ ^{13}C NMR spectra showed a difference of 2 ppm (Fig. 2D) that justifies also a powerful metal–4 interaction.

The complementary plots depicted in Fig. 3 and 4, showing the variation of $\Delta\delta$ (difference in the chemical shift = $\delta_{4\cdot\text{M}} - \delta_4$) against the concentration $4\cdot\text{M}^{x+}$ (mmol mL^{-1}), provide the best visual behavior of the chelating process. So, this quantitative analysis revealed that, independently of the number of coordinating molecules of DMSO solvating both cations, the preference towards three ligands 4 by the thorium(IV) species contrasted with the affinity of the uranium(VI) units by only one 1,3-dicarbonyl ligand 4. Fig. 3 and 4 illustrate all these results. The uranyl cation only exhibited a weak interaction with one ligand 4 due to the low increment of the chemical shift of the 7.95 ppm singlet observed *versus* the analogous chemical shift of pure molecule 4 ($\Delta\delta \sim 0.005$ ppm) (Fig. 3). The analysis of the same effect in the formation of the $[\text{Th}] \cdot 4_3$ indicated a stronger metal–ligand interaction due to a larger $\Delta\delta \sim 0.009$ ppm (Fig. 4A). However, the highest signal displacement (almost 0.011 ppm) was detected for the doublet placed at 7.73 ppm (Fig. 4B).

An ATR-FTIR study was employed to confirm the strongest interaction detected between 4 and thorium(IV) rather than the TSIL 4 with uranium(VI) species. The samples were prepared in a solution in the smallest amount of DMSO and methanol and, after mixing the components and refluxing for 1 h, the solvent

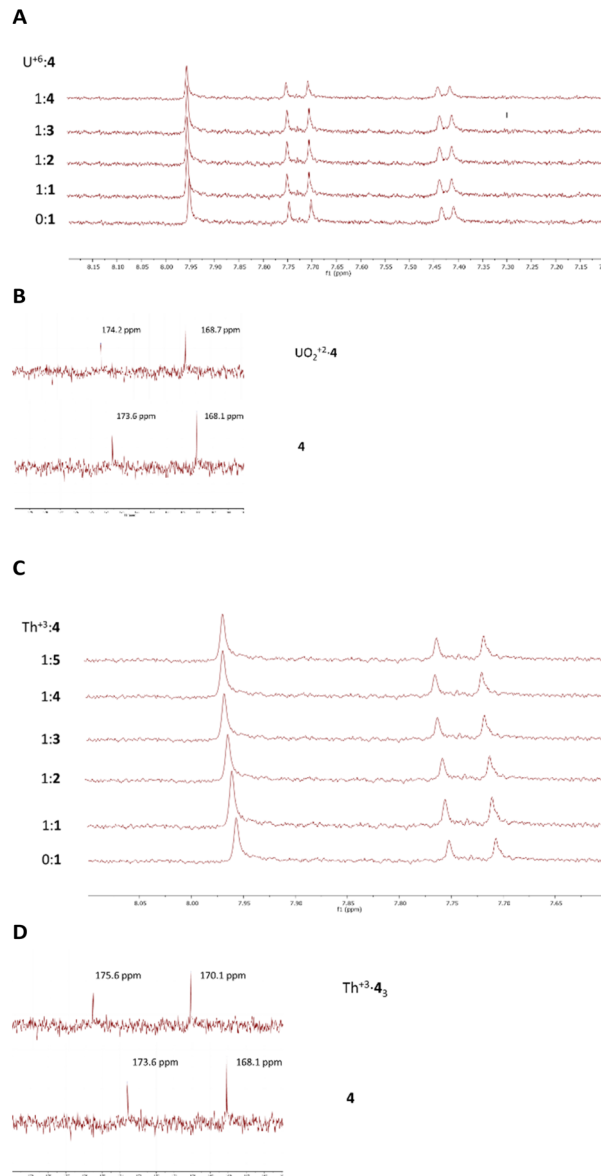


Fig. 2 (A) Stack plot of the titration results of uranyl nitrate with 4 monitored by ^1H NMR spectroscopy. (B) Comparison of chemical shifts of ^{13}C NMR for free ligand 4 and the mixture $\text{UO}_2^{2+} \cdot 4$. (C) Stack plot of the titration results of thorium(IV) nitrate with 4 monitored by ^1H NMR spectroscopy. (D) Comparison of chemical shifts of ^{13}C NMR for free ligand 4 and the mixture $\text{Th}^{3+} \cdot 4_3$. All experiments were recorded using $\text{DMSO}-d_6$.

was evaporated under vacuum. The remaining DMSO, the ciprofloxacin fingerprint signals, and the absorption peaks of the corresponding cations offered a small window of the infrared region ($1450\text{--}1790\text{ cm}^{-1}$) in which band shifting could be detected. Peaks around $800\text{--}1000$ and $1000\text{--}1100\text{ cm}^{-1}$, which correspond to the UO_2^{2+} cation, could not be observed due to the presence of an intense and wide absorption band. Thus, mixtures of pure 4, 3 : 1 $[\text{TSIL}(\text{4})] : [\text{Th}^{4+}]$ and 1 : 1 $[\text{TSIL}(\text{4})] : [\text{U}^{6+}]$ were separately suspended in DMSO/methanol and then refluxed for 1 h. After evaporation of the solvent the sticky powders were analysed. Fig. 5 reveals a significant downward



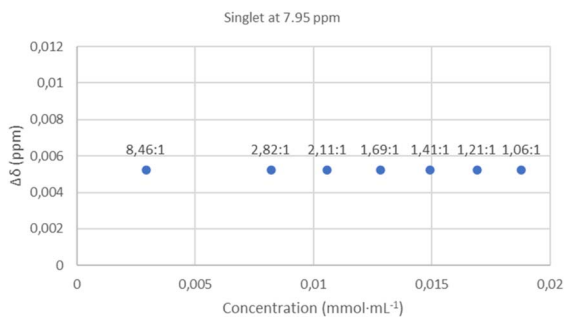


Fig. 3 Plot of the variation of the chemical shift (in ppm) versus concentration of the TSIL 4 during the titration of uranyl nitrate monitored by ^1H NMR spectroscopy.

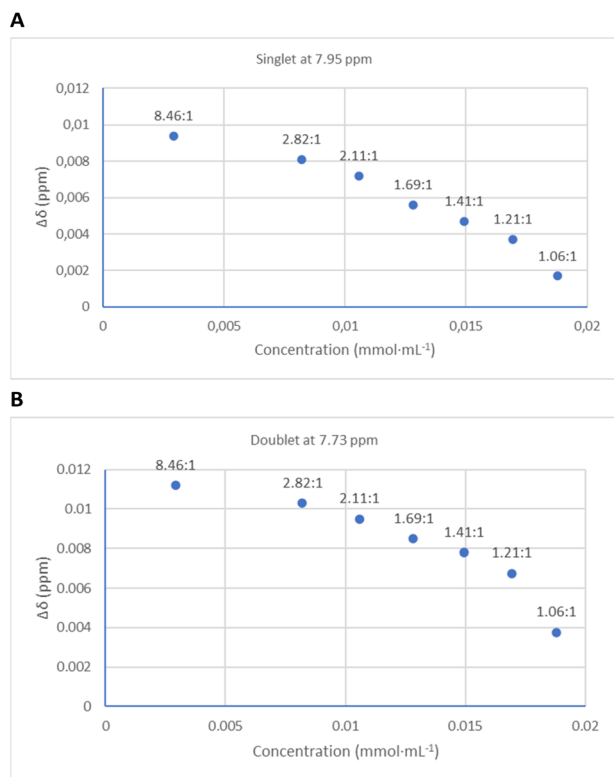


Fig. 4 Plot of the variation of the chemical shift (in ppm) versus concentration of the TSIL 4 during the titration of thorium(IV) nitrate monitored by ^1H NMR spectroscopy. (A) For the singlet located at 7.95 ppm; (B) for the doublet observed at 7.73 ppm.

shift to lower wave numbers for the carbonyl group stretching frequency from 1736 cm^{-1} to 1716 cm^{-1} and from 1681 cm^{-1} to 1663 cm^{-1} . The metal–O interactions forced a reduction of the bond order of the 1,3-dicarbonylic moiety. Unfortunately, crystalline structures could not be isolated to determine the real coordination environment of the metal.

DFT-based computational optimization of the complexes

The X-ray diffraction analyses of solid samples of the corresponding metal–cyproflaxacin aggregates could not be


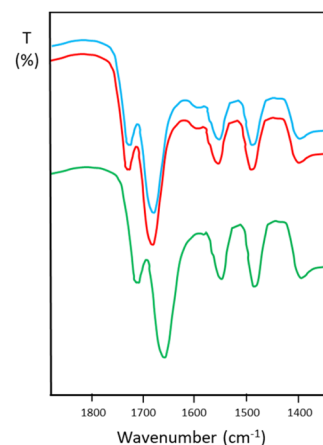


Fig. 5 Infrared spectra of TSIL (4) (red), $[\text{TSIL (4)}]_3 \cdot [\text{Th}^{4+}]$ (green) and $[\text{TSIL (4)}] \cdot [\text{U}^{6+}]$ (blue) focused on the carbonyl stretching region. ATR-FTIR of the neat sticky powder resulting after evaporating MeOH of the corresponding mixtures.

successfully completed. This fact moved us to analyze the observed coordinative preferences of both metals with the ligand 4. Hexacoordination of the uranyl cation is very well documented^{71,72} and this strict profile contrasts with the variable coordination of the thorium(IV). The ability of thorium to coordinate in different geometries and a wide range of coordination numbers confirm the difficulty to predict its preferred geometry.⁷³ Within this complex scenario, we decided to perform DFT calculations trying to shed light on the different behavior observed for uranyl and thorium(IV) complexes (see the ESI† for computational details).

All the microextractions and other tests, such as loading of the extractive mixtures, as well as the solution stability studies, were conducted with the corresponding metal nitrates. The acidic pH for the selective extraction was achieved using nitric acid, so we focused our attention on these species whose internal spheres were surrounded by nitrate anions and water molecules. In order to simplify the model of calculations the energies corresponding to the substitution of molecules of water by ligand 4 units (Scheme 2) in an aqueous environment were obtained.

We hypothesize that the extraction coefficients are related with the water–TSIL(4) exchange equilibrium where 4·metal complexes will be extracted in the IL phase, whereas water complexes would remain in the aqueous phase. In that sense, enhanced extraction coefficients would be related to the exergonic character of the exchange reaction. In contrast, low extraction coefficients would be related to endergonic reactions

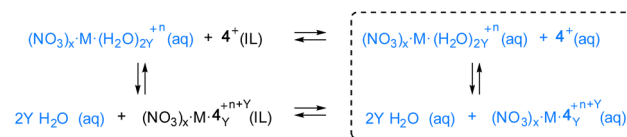

Scheme 2 Simplified model for DFT calculations of $\text{M}-4_Y$ formation.



[note that in the proposed reaction, two molecules of water are exchanged by one molecule of **4**].

Given the plethora of possible coordination patterns and metal:ligand ratio combinations, especially in the case of thorium, the coordination number for the uranyl cation was fixed at six and the selected coordination numbers for thorium(IV) were ten and eight because they are the most frequent coordination numbers reported for this cation.⁷² In addition, we took advantage of the spectroscopic results, so compounds with a 1:1 ratio for the uranyl nitrate:TSIL **4** complex and 1:3 thorium(IV) nitrate:TSIL **4** complex were considered respectively (*vide supra*). The obtained results indicated that the water–ligand exchange is not thermodynamically favored for uranyl nitrate as shown by the Gibbs reaction energy value of +1.8 kcal mol⁻¹. As a consequence, only residual extraction of uranyl nitrate is expected (Fig. 6A).

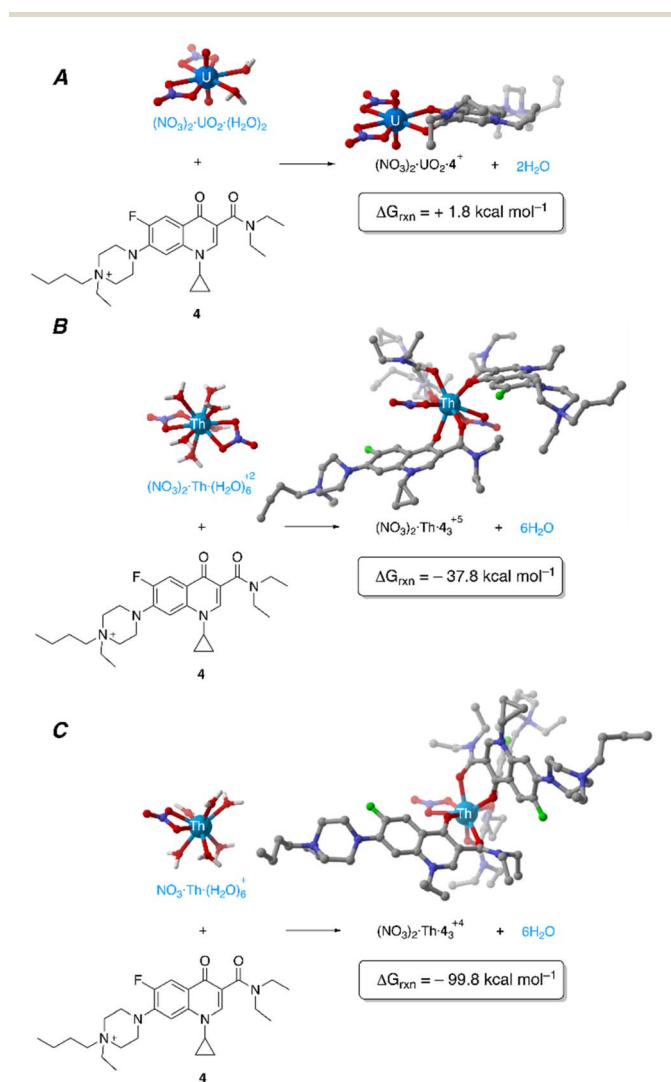


Fig. 6 Reaction Gibbs free energies associated with the water–4 exchange of (A) uranyl nitrate or (B) thorium(IV) nitrate complexes (coordination number = 10) and (C) thorium(IV) nitrate complex (coordination number = 8) computed at the PBE0(PCM)/6-31 G(d) &SDD level of theory.

The Gibbs free energies of the thorium(IV) complexes with the different most abundant coordination numbers (eight and ten)⁷² were calculated independently (Fig. 6B and C). In this case, our calculations indicated that the water–ligand exchange process is strongly favored for thorium(IV) nitrate both considering 10 and 8 coordinated complexes (Gibbs reaction energy of -31.8 kcal mol⁻¹ or -99.8 kcal mol⁻¹, respectively). Therefore, complete extraction of thorium(IV) is theoretically assessed, in good agreement with the experimental evidence (see the ESI† for further information about the equilibrium reaction of other complexes presumably involved). Moreover, the computed data revealed that these two possible complexes of thorium bearing three units of ligand **4** and different number of nitrate anions (apart from others in equilibrium) can exist in the solution making it very difficult to obtain a pure monocystal.

Kinetic analysis and loading tests

The kinetics of the affinity of the TSIL compound **4** towards the thorium(IV) cation at pH = 1 was next evaluated using ICP as a detection technique. In this first experiment, an aqueous 0.1 M solution of thorium(IV) nitrate (5 mL) was extracted with a 0.1 M solution of **4** in [BMIM][Tf₂N] (1 mL). Using an excess of thorium cations in the aqueous solution to be extracted (Fig. 7a), the amount of the extracted thorium(IV) remained constant at 10 min. The maximum amount of metal cation reached 0.033 mmol approximately, which is in agreement with the already mentioned most stable geometry of Th^{IV}·4₃.

Under the same conditions, a second experiment was run using an aqueous 6.7 × 10⁻³ M solution of thorium(IV) nitrate (5 mL), which was extracted with a 0.1 M solution of **4** in [BMIM][Tf₂N] (1 mL). Here, the final 1:3 metal:TSIL **4** ratio was again confirmed and the kinetics were very similar to the previous test, completing the overall extraction in 10–11 min (Fig. 7b).

The kinetics of the extractive system (0.1 M solution of **4** in [BMIM][Tf₂N], 1 mL) versus an original solution (5 mL) containing 0.1 M solution of both thorium(IV) and uranyl nitrates was assessed (Fig. 8). The extraction profile of the thorium

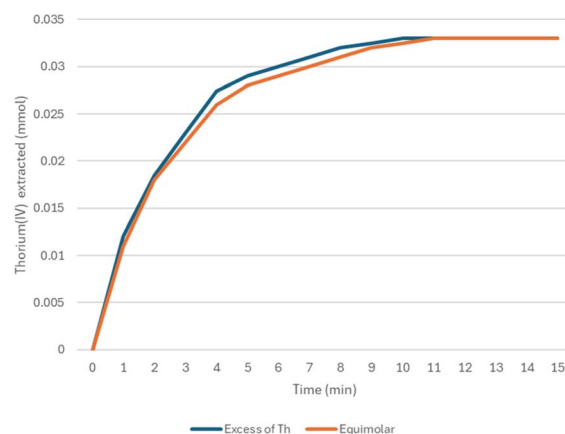


Fig. 7 (a) Kinetics of the extraction of thorium(IV) by **4**/[BMIM][Tf₂N] using an excess of the metal cation in the original solution (blue plot). (b) Kinetics of the extraction of a more diluted thorium(IV) solution by **4**/[BMIM][Tf₂N] working with a final 3:1 **4**:Th^{IV} ratio (orange plot).




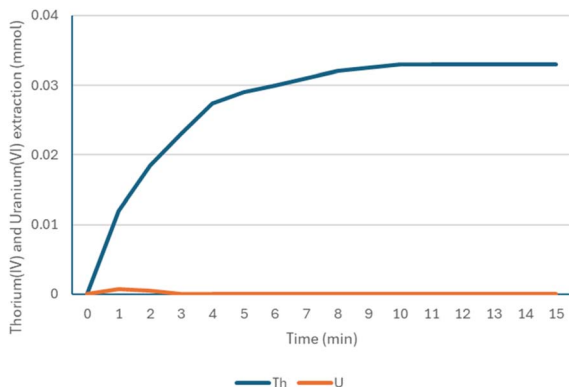


Fig. 8 Competitive extraction of 0.1 M of both thorium(IV) and uranyl nitrate with 0.1 M solution of **4** in [BMIM][Tf₂N].

cation was identical to the plot observed in Fig. 7A. However, the uranyl cation was slightly extracted at the earlier stages of the extractive sequence but finally, after 3 min, the complexation of ligand **4** with uranium(VI) was extremely low.

The plot fragment between 0 and 3 min in Fig. 8 suggests that thorium captured the ligand initially bound to the uranyl cation. Thus, a solution of uranyl nitrate (0.2 M, 1 mL) at pH = 1, and a solution of **4** in [BMIM][Tf₂N] (0.1 M, 1 mL) were stirred vigorously for 1 h at 25 °C. After separation of both phases, the aqueous one was discarded and the IL phase was analyzed by ICP (after the digestion and the appropriate preparation of the sample). The final amount of the uranium(VI) species revealed that 0.090 mmol of them were ligated to the IL system. Next, this organic solution was mixed with a thorium nitrate solution (0.035 M, 1 mL) at pH = 1 and the liquid was vigorously stirred for 10 min at 25 °C. The two phases were separated and analyzed by ICP obtaining Th(IV) in the aqueous portion, whilst all the thorium(IV) was concentrated in the IL medium (eqn (2)).



A ternary combination of metals composed of thorium(IV), scandium(III) and uranyl nitrates was analogously assessed under the identical experimental pathway showing the same behavior (see the Experimental section). Therefore, the selective extraction of thorium(IV) versus other different metal cations can be extrapolated. However, the main aim of this article is to

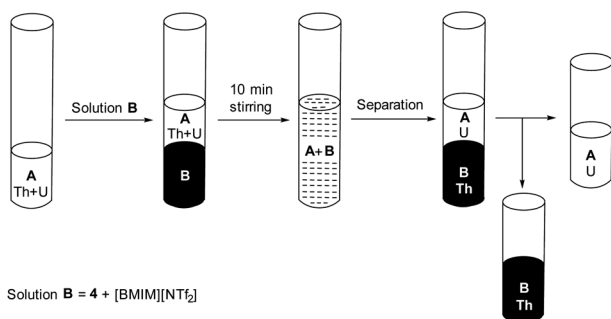


Fig. 9 General procedure for the selective extraction of thorium(IV).

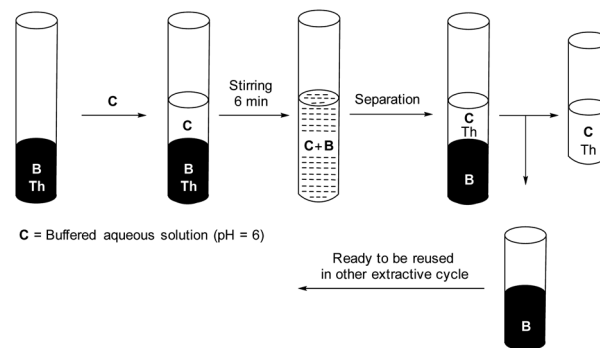


Fig. 10 General procedure for the selective stripping of thorium(IV).

highlight the selectivity of the extraction of thorium versus uranium.

Optimal loading of the extractive solution and recycling studies

Several protocols were designed to determine the optimum loading of the extractive mixture and its stability to run several cycles for an efficient recovery. The extraction of solution A was performed by stirring the mixed phases (A + B) for 10 min followed by the separation of the aqueous phase (A) containing the uranium and the IL phase (B) with the thorium(IV) cation (Fig. 9).

The stripping process recovering the IL phase (B) without the thorium(IV) cation was carried out according to Fig. 10. For this purpose, a phosphate buffered aqueous solution at pH = 6 (solution C) was added to solution B and the resulting mixture stirred for 6 min (see below). Thorium(IV) was dissolved in the C solution whilst the B solution was reused in another extractive process. The yield of the extraction was 98% (according to ICP analysis).

Following these two procedures, the optimal concentration of **4** in [BMIM][Tf₂N] was assessed, determining the most appropriate one ensuring a total recovery of the IL solution B. Three different concentrations of **4** in [BMIM][Tf₂N] were tested, 0.5 M, 0.4 M and 0.3 M. To our surprise, the solution with the highest concentration seemed unstable once the metal is fully

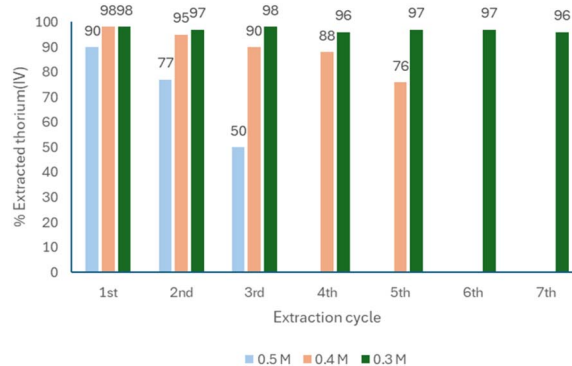


Fig. 11 Stability of the concentration of **4** in [BMIM][Tf₂N] after extraction of thorium(IV) and its recovery.



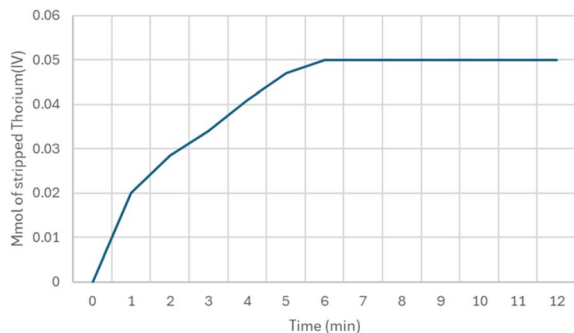


Fig. 12 Kinetics of the stripping process of thorium(IV) at pH = 6.

coordinated by the ligand (Fig. 11). 0.4 M solution was appropriate at the beginning but, after the 4th extractive cycle, the yield of the recovery was reduced to 88%. The optimal concentration was 0.3 M, which can be used for more than seven cycles, maintaining stripping yields higher than 96% (Fig. 11).

Finally, the kinetics of the stripping sequence were studied following the protocol of Fig. 10 using a 0.3 M solution of **4** in [BMIM][Tf₂N]. In the plot of Fig. 12 the constant amount of the stripped thorium(IV) was found after 6 min.

Conclusions

The solution of **4**, a TSIL derived from ciprofloxacin, in [BMIM][Tf₂N] (as an IL solvent) was extremely efficient for the extraction of thorium(IV) cations *versus* uranium(VI) at pH = 1. The spectroscopic tests confirmed that three ligands **4** coordinated strongly to a single thorium(IV) cation whilst only one ligand **4** was very weakly coordinated with the uranyl cation. The simplified aqueous model, established for DFT calculations, confirmed the high affinity of **4** with thorium(IV) in several coordination (8 and 10) modes. The stability of the optimal solution of **4** in the IL was 0.3 M for the extraction and the mixing time for extraction was 11 min. The recycling of the resulting IL mixture was very satisfactory up to the 7th batch using a stripping process at pH = 6 for 6 min. The designed kinetic models could be considered as a very important tool for predicting the appropriate extraction processes. This prototype is ready to be implemented in mining selective extraction or even in the separation of metals from the radioactive waste mixtures in nuclear power plants.

In comparison with the three more representative examples reported in the literature (to the best of our knowledge) where excellent extractions of thorium(IV) *vs.* uranium(VI) were demonstrated, here we reported the most comprehensive environmental/sustainable system. The separation by employing the recyclable sulfonated membrane³⁴ showed excellent selectivity for the separation of thorium *vs.* uranium(VI) and two rare earth elements. Here, the recovery of thorium(IV) is very high but with lower K than the analogous ones obtained in this study. Similar conclusions can be deduced comparing the MOF-LIC-1 system.³⁵ In addition, in the titled method a complete multimetallic test confirmed its preference for thorium(IV).

Finally, the phosphoramidate-based RTIL method⁴³ showed comparable extractive results with high efficiency of the recovery step. However, the procedure involved chloroform as a co-solvent, which is not desirable in a high scale procedure.

Experimental section

General remarks

Reagents and solvents were purchased from commercial suppliers and used as received. Low-resolution mass spectra (EI) were obtained with an Agilent GC/MS5973N spectrometer at 70 eV, with fragment ions in *m/z* and relative intensities (%) in parentheses. NMR spectra were recorded at 300 or 400 MHz for ¹H NMR, at 75 or 100 MHz for ¹³C NMR and at 282 or 376 MHz for ¹⁹F NMR with a Bruker AV300 Oxford or a Bruker AV400 spectrometer, respectively, using CDCl₃ as solvent, and TMS as an internal standard (0.00 ppm). The data are reported as: s = singlet, d = doublet, t = triplet, q = quartet, m = multiplet or unresolved, br s = broad signal, coupling constant(s) in Hz, integration. ¹³C NMR spectra were recorded with ¹H-decoupling at 100 MHz and referenced to CDCl₃ at 77.16 ppm. ¹⁹F NMR spectra were recorded with ¹H-decoupling and referenced to CF₃CO₂H at -76.6 ppm. ICP and microanalyses were performed using a PerkinElmer Optima 7300 DV and a LECO Micro TruSpec, respectively.

Synthesis of 1-cyclopropyl-7-(4-ethylpiperazin-1-yl)-6-fluoro-4-oxo-1,4-dihydroquinoline-3-carboxylic acid (2). To a solution of ciprofloxacin hydrochloride (3.1 g, 8.0 mmol) and DIPEA (6.7 equiv., 9.3 mL, 6.9 g, 54 mmol) in MeCN:H₂O (1:1, 30 mL mmol⁻¹, 240 mL), bromoethane (5.0 equiv., 3.0 mL, 4.4 g, 40 mmol) was added dropwise at 0 °C. Potassium iodide (10 mol%, 132 mg, 0.8 mmol) was then added at the same temperature. The mixture was stirred at 0 °C for 1 h and then it was heated to 40 °C and it was stirred at this temperature for 16 h. The solvent was removed under reduced pressure and the residue was dissolved in DCM (40 mL), washed with a phosphate buffer solution at pH = 6.5 (30 mL) and dried with MgSO₄. The solvent was removed under reduced pressure and pure compound **2** was obtained without further purification (2.6 g, 7.4 mmol, 92%) as a white solid; ¹H NMR (300 MHz, CDCl₃) δ 8.75 (s, 1H), 7.99 (d, *J* = 13.1 Hz, 1H), 7.36 (d, *J* = 7.1 Hz, 1H), 3.58–3.52 (m, 1H), 3.39–3.34 (m, 4H), 2.73–2.65 (m, 4H), 2.52 (q, *J* = 7.2 Hz, 2H), 1.42–1.32 (m, 2H), 1.22–1.18 (m, 2H), 1.15 (t, *J* = 7.2 Hz, 3H), *Proton from the carboxylic acid was not observed; ¹³C NMR (101 MHz, CDCl₃) δ 177.2, 167.8, 153.8 (d, *J* = 252.5 Hz), 147.5, 146.1 (d, *J* = 10.1 Hz), 139.2, 119.8 (d, *J* = 8.1 Hz), 112.4 (d, *J* = 24.2 Hz), 108.2, 104.9, 52.5 (2C), 52.4, 49.9 (2C), 35.4, 12.0, 8.3 (2C); ¹⁹F NMR (282 MHz, CDCl₃) δ -120.6 (s, 1F); IR (neat) ν_{max} 3420–3395, 1707–1675 cm⁻¹; LRMS (EI) *m/z* 360 (M⁺ + 1, 16%), 359 (M⁺, 69%), 344 (24), 316 (21), 315 (100), 287 (13), 257 (13), 230 (12), 150 (10), 84 (24), 70 (12), 57 (32), 56 (11), 44 (27), 42 (19). Elemental analysis calcd for C₁₉H₂₂FN₃O₃: C, 63.50; H, 6.17; F, 5.29; N, 11.69; O, 13.35. Found: C, 63.3; H, 6.5; N, 11.5.

Synthesis of 1-cyclopropyl-*N,N*-diethyl-7-(4-ethylpiperazin-1-yl)-6-fluoro-4-oxo-1,4-dihydroquinoline-3-carboxamide (3). To a solution of **2** (546 mg, 1.50 mmol) and Et₃N (3.00 equiv., 0.64 mL, 0.45 g, 4.50 mmol) in DCM (3 mL), diethylamine (3.00



equiv., 0.47 mL, 329 mg, 4.50 mmol) and thionyl chloride (1.10 equiv., 0.12 mL, 196 mg, 1.65 mmol) were added dropwise at 0 °C and the mixture was stirred at this temperature for 30 min. The solvent and the volatile compounds were removed under reduced pressure. The residue was dissolved in CHCl₃ (30 mL), washed with a saturated aqueous solution of sodium bicarbonate (3 × 15 mL), then washed again with a saturated aqueous solution of potassium carbonate (3 × 10 mL) and dried with MgSO₄. The solvent was removed under reduced pressure and the residue was purified by recrystallization with Et₂O to yield pure compound 3 (590 mg, 1.42 mmol, 95%) as a yellowish solid; ¹H NMR (400 MHz, CDCl₃) δ 7.93 (d, *J* = 13.2 Hz, 1H), 7.91 (s, 1H), 7.26 (d, *J* = 7.1 Hz, 1H), 3.55 (q, *J* = 7.1 Hz, 2H), 3.45–3.25 (m, 7H), 2.81 (br s, 4H), 2.64 (d, *J* = 7.4 Hz, 2H), 1.30–1.20 (m, 8H), 1.14–1.09 (m, 5H); ¹³C NMR (101 MHz, CDCl₃) δ 172.6, 166.7, 153.8 (d, *J* = 248.0 Hz), 144.3 (d, *J* = 11.3 Hz), 142.9, 138.6, 121.8 (d, *J* = 7.0 Hz), 119.4, 112.7 (d, *J* = 22.7 Hz), 104.8, 52.4, 49.6 (2C), 43.3 (2C), 39.6 (2C), 34.2, 14.6, 13.1 (2C), 8.3 (2C); ¹⁹F NMR (282 MHz, CDCl₃) δ –123.7 (s, 1F); LRMS (EI) *m/z* 414 (M⁺, 18%), 342 (12), 316 (21), 315 (100). Elemental analysis calcd for C₂₃H₃₁FN₄O₂: C, 66.64; H, 7.54; F, 4.58; N, 13.52; O, 7.72. Found: C, 68.06; H, 7.84; N, 13.86.

Synthesis of 7-(4-butyl-4-ethyl-4-((1,1,1-trifluoro-*N*-((trifluoromethyl)sulfonyl)methyl)sulfonamido)-4λ⁵-piperazin-1-yl)-1-cyclopropyl-*N,N*-diethyl-6-fluoro-4-oxo-1,4-dihydroquinoline-3-carboxamide (4). A solution of 3 (207 mg, 0.50 mmol) and iodobutane (2.00 equiv., 0.11 mL, 184 mg, 1.00 mmol) in MeCN (8 mL) was stirred at 80 °C for 48 h. The solvent was removed under reduced pressure. The residue was dissolved in CHCl₃ (10 mL), an aqueous solution of lithium bistriflimide (1.30 equiv., 0.65 mmol, 0.5 M, 1.3 mL) was added and the mixture was stirred at 25 °C for 15 h. Then, the aqueous phase was extracted with CHCl₃ (15 mL) and the combined organic fractions were washed with H₂O (2 × 10 mL) and dried with MgSO₄. The solvent was removed under reduced pressure and the residue was purified by recrystallization with EtOAc to yield pure compound 4 (330 mg, 0.44 mmol, 89%) as a white solid; ¹H NMR (400 MHz, CDCl₃) δ 8.03 (s, 1H), 7.91 (d, *J* = 14.3 Hz, 1H), 7.59 (d, *J* = 7.2 Hz, 1H), 3.91–3.56 (m, 11H), 3.53–3.33 (m, 5H), 2.89–2.57 (m, 2H), 1.79–1.60 (m, 2H), 1.53–1.45 (m, 4H), 1.41–1.34 (m, 3H), 1.26–1.16 (m, 7H), 1.04 (t, *J* = 7.3 Hz, 3H); ¹³C NMR (101 MHz, CDCl₃) δ 172.6, 167.1, 152.0 (d, *J* = 247.5 Hz), 141.9 (d, *J* = 11.0 Hz), 140.9, 138.8, 121.7 (d, *J* = 6.6 Hz), 120.2 (q, *J* = 259.0 Hz, 2C), 118.3, 111.6 (d, *J* = 21.9 Hz), 106.7, 58.4, 57.8 (2C), 52.4, 43.2 (2C), 34.7 (2C), 29.1, 23.4, 19.7, 14.5, 13.6 (2C), 8.2, 7.2 (2C); ¹⁹F NMR (282 MHz, CDCl₃) δ –77.8 (s, 6F); –125.2 (s, 1F); LRMS (EI) *m/z* 471 (M⁺, 21%), 315 (100), 236 (33). Elemental analysis calcd for C₂₉H₄₀F₇N₅O₆S₂: C, 46.33; H, 5.36; F, 17.69; N, 9.32; O, 12.77; S, 8.53. Found: C, 46.8; H, 5.5; N, 9.4; S 8.5.

General procedure for the selective extraction of thorium versus uranium

To extract the analytes (thorium and uranium) from an aqueous sample A (5 mL of both 0.1 M thorium nitrate and 0.1 M uranyl nitrate), the pH of this sample was adjusted to 1.0 with 1 M aqueous solution of HNO₃. Then, the extractant [5 mL of a 0.3 M

solution of compound 4 in [BMIM][NTf₂] (5)] was added and the solution was stirred for 11 minutes using a vortex mixer. The mixture was then allowed to rest and the two phases were separated. Thorium was extracted in solution B (II), while uranium remains in the aqueous sample A. Fig. 9 shows a detailed scheme of the selective extraction process of thorium versus uranium.

Yield of extracted thorium(IV) >99.5% (from ICP-MS data analysis). Uranium(VI) content in solution A >99.5% (from ICP-MS).

General procedure (stripping) for the liberation of the extracted metal and recuperation of the extraction system (4 in 5)

To remove the thorium from solution B and recover the extraction system (4 in 5), a dihydrogen–monohydrogen phosphate buffer solution at pH = 6.0 (solution C, 5 mL) was added to solution B (4 in 5 saturated in thorium, 5 mL). The mixture was stirred in a vortex mixer for 7 min. The mixture was then allowed to rest and the two phases were separated. Thorium was extracted in aqueous phase C, and the extraction system 4 + 5 was recovered (B). Fig. 10 shows a detailed scheme of the recovery of the extraction system. The thorium recovery was higher than 98% (from ICP-MS data analysis) and the recovered extraction system could be used in subsequent extraction cycles.

Data availability

NMR spectra of all new compounds, kinetics of a ternary component extraction survey and DFT models with their Cartesian coordinates are included in the ESI.† “This material is available free of charge *via* the Internet at <https://pubs.acs.org>”.

Author contributions

Dr D. L. and A. S. performed the experimental work and the revision of the article (investigation and methodology). A. d. C. performed all the computational work. H. Q. N. G. supervised the international collaboration and conceptualization. G. G. and J. M. S. directed and supervised all the studies, experiments, conceptualization, funding acquisition, project administration, and writing the original manuscript and the corresponding revisions and editions.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge the continued financial support from the Spanish Ministerio de Economía y Competitividad (CTQ2017-85093-P) and Ministerio de Ciencia, Innovación y Universidades (RED2018-102387-T, RED2022-134287-T, PID2019-104772GB-I00 and PID2019-107268GB-I00) funded by MCIN/AEI/10.13039/501100011033 and the Grant IT1553-22, funded by the Gobierno Vasco/Eusko Jaurlaritz. Generalitat Valenciana-



Conselleria de Educaci3n, Cultura, Universidades y Empleo (IDIFEDER/2021/013, GVA-COVID19/2021/079), Medalchemy S. L. (Medalchemy-22T) and the University of Alicante (VIGROB-050; UADIF17-42 UAUSTI16-02, VIGROB-068 and UAUSTI21-05). The authors also thank the SGI/IZO-SGIker of the UPV/EHU and DIPC for the generous allocation of analytical and computational resources. David Lled3 thanks the Spanish Ministerio de Ciencia, Innovaci3n y Universidades for the fellowship (FPU15/00097).

Notes and references

- Nuclear Energy*, ed. R. L. Murray and K. E. Holbert, Elsevier Inc., Oxford, UK, 5th edn, 2020.
- Encyclopedia of Nuclear Energy*, E. Greenspan, Elsevier Inc., Oxford, UK, 1st edn, 2021.
- C. Degueldre and M. J. Joyce, Evidence and uncertainty for uranium and thorium abundance: A review, *Prog. Nucl. Energy*, 2020, **124**, 103299.
- V. K. Manchanda, Thorium as an abundant source of nuclear energy and challenges in separation science, *Radiochim. Acta*, 2023, **111**, 243–263.
- M. J. Joyce, in *Nuclear Engineering*, Elsevier, Oxford, UK, 2018, ch. 5, pp. 87–110.
- M. Makvandi, E. Dupis, J. W. Englen, F. M. Nortier, M. E. Fassbender, S. Simon, E. R. Birnbaum, R. W. Atcher, K. D. John, O. Rixe and J. P. Norenberg, Alpha-emitters and targeted alpha therapy in oncology: from basic science to clinical investigations, *Targeted Oncol.*, 2018, **13**, 189–203.
- V. K. Manchanda and P. N. Pathak, Amides and diamides as promising extractants in the back end of the nuclear fuel cycle: an overview, *Sep. Purif. Technol.*, 2004, **35**, 85–103.
- Z. Li, Z. Zhang, S. Qi, L. Zhao, J. Pan, Z. Feng and X. Huang, Stripping and recovery of U and Th from EHEHPA in rare earth separation plant, *Sep. Purif. Technol.*, 2024, **331**, 125423.
- C. Jin, X. Yang, D. Fang, S. Ni, S. Wang, A. Ding, P. Cen and C. Xiao, Selective separation of radioactive thorium and uranium from scandium using N-heterocyclic carboxamide ligands, *Sep. Purif. Technol.*, 2024, **328**, 125028.
- F. Aydin, E. Yilmaz, G. Demirkiran, Z. Erbas, M. Vurucuel and M. Soylak, TiO₂@ZnO nanocomposite: bifunctional material for solid phase extraction of U(VI) and Th(IV) and photocatalytic degradation of organic contaminant, *J. Radioanal. Nucl. Chem.*, 2023, **332**, 3879–3892.
- S. Wang, X. Yang, L. Xu, Y. Miao, X. Yang and C. Xiao, Selective Extraction of Uranium(VI) from Thorium(IV) Using New Unsymmetrical Acidic Phenanthroline Carboxamide Ligands, *Ind. Eng. Chem. Res.*, 2023, **62**, 15613–15624.
- V. M. Telmore, P. Kumar, P. G. Jaison, A. Mhatre and H. Naik, High performance liquid chromatographic separation of ^{228,229}Th and ^{232,233}U and their estimation by α - and γ -ray spectrometry, *J. Radioanal. Nucl. Chem.*, 2017, **313**, 319–326.
- S. A. Allahyari, S. J. Ahmadi, A. Minuchehra and A. Charkhi, Th(IV) recovery from aqueous waste via hollow fiber renewal liquid membrane (HFRLM) in recycling mode: modelling and experimental validation, *RSC Adv.*, 2017, **7**, 7413–7423.
- A. K. Dinkar, S. K. Singh, S. C. Tripathi, R. Verma and A. V. R. Reddy, Carrier mediated transport of thorium from nitric acid medium using 2-ethyl hexyl hydrogen 2-ethyl hexyl phosphonate (PC88A)/N-dodecane as carrier, *Sep. Sci. Technol.*, 2013, **48**, 728–735.
- C. S. Kedari, S. S. Pandit and P. M. Gandhi, Separation by competitive transport of uranium(VI) and thorium(IV) nitrates across supported renewable liquid membrane containing trioctyl phosphineoxide as metal carrier, *J. Membr. Sci.*, 2013, **430**, 188–195.
- S. Panja, P. K. Mohapatra, S. C. Tripathi and V. K. Manchanda, Transport of thorium(IV) across a supported liquid membrane containing N,N,N',N'-Tetraoctyl-3-oxapentanediamide (TODGA) as the Extractant, *Sep. Sci. Technol.*, 2010, **45**, 1112–1120.
- T. P. Rao, P. Metilda and J. M. Gladis, Preconcentration techniques for uranium(VI) and thorium(IV) prior to analytical determination-an overview, *Talanta*, 2006, **68**, 1047–1064.
- R. G. Silva, C. A. Morais and E. D. Oliveira, Selective precipitation of rare earth from non-purified and purified sulfate liquors using sodium sulfate and disodium hydrogen phosphate, *Miner. Eng.*, 2019, **134**, 402–416.
- S. Sadeghi and A. Davami, A rapid dispersive liquid-liquid microextraction based on hydrophobic deep eutectic solvent for selective and sensitive preconcentration of thorium in water and rock samples: A multivariate study, *J. Mol. Liq.*, 2019, **291**, 111242.
- M. A. Didi, D. Villemin, O. Abderrahim and A. Azzouz, Liquid-liquid extraction of thorium(IV) by fatty acids: a comparative study, *J. Radioanal. Nucl. Chem.*, 2014, **299**, 1191–1198.
- J. Su, R. Xu, S. Ni, F. Li and X. Sun, A cost-effective process for recovering thorium and rare earths from radioactive residues, *J. Cleaner Prod.*, 2020, **254**, 119931.
- F. Li, Z. Yang, H. Weng, G. Chen, M. Lin and C. Zhao, High efficient separation of U(VI) and Th(IV) from rare earth elements in strong acidic solution by selective sorption on phenanthroline diamide functionalized graphene oxide, *Chem. Eng. J.*, 2018, **332**, 340–350.
- A. M. Safulina, D. V. Ivanets, E. M. Kudryavtsev, D. V. Baulin, V. E. Baulin and A. Y. Tsvadze, Extraction of f-elements by binary extractants based on 1,5-bis[*o*-(dioxophosphoryl)phenoxy]-3-oxapentane derivatives and trioctylamine, *Russ. J. Inorg. Chem.*, 2018, **63**, 1679–1683.
- A. H. Orabi, B. T. Mohamed, D. A. Ismaiel and S. S. Elyan, Sequential separation and selective extraction of uranium and thorium from monazite sulfate leach liquor using dipropylamine extractant, *Miner. Eng.*, 2021, **172**, 107151.
- R. R. Pawar, V. J. Suryavanshi, S. T. Salunkhe, S. S. Patil and G. N. Mulik, Liquid-liquid extraction of thorium(IV) with *N*-*n*-heptylaniline from acid media, *J. Radioanal. Nucl. Chem.*, 2017, **311**, 419–426.
- For the employment of 4-methyl-*N*-*n*-octylaniline as an extracting agent, see: P. S. More, U. B. Barache,



- S. H. Gaikwad and L. V. Gavali, Extraction of Th(IV) and U(VI) with 4-methyl-N-n-octylaniline as an extracting agent, *J. Radioanal. Nucl. Chem.*, 2022, **331**, 4149–4158.
- 27 P. K. Tarafder, S. K. Pradhan and R. K. Mondal, Separation of thorium by facile liquid–liquid extraction, and its rapid spectrophotometric and ICP-AES determination in rocks and minerals, *J. Radioanal. Nucl. Chem.*, 2016, **309**, 1021–1028.
- 28 V. G. Maiorov and A. I. Nikolaev, Extraction of Th(IV) with tributyl phosphate from aqueous HCl solutions containing sodium, calcium, or aluminum chloride, *Russ. J. Appl. Chem.*, 2006, **79**, 1196–1199.
- 29 D. R. Prabhu, A. Sengupta, M. S. Murali and P. N. Pathak, Role of diluents in the comparative extraction of Th(IV), U(VI) and other relevant metal ions by DHOA and TBP from nitric acid media and simulated wastes: Reprocessing of U–Th based fuel in perspective, *Hydrometallurgy*, 2015, **158**, 132–138.
- 30 B. Gupta, P. Malik and A. Deep, Extraction of uranium, thorium and lanthanides using Cyanex-923: Their separations and recovery from monazite, *J. Radioanal. Nucl. Chem.*, 2002, **251**, 451–456.
- 31 P. S. Mansingh, V. Chakravorty and K. C. Dash, Solvent Extraction of Thorium(IV) by Cyanex 272/Cyanex 302/Cyanex 301/PC-88A and their Binary Mixtures with TBP/DOSO from Aq. HNO₃ and H₂SO₄ Media, *Radiochim. Acta*, 1996, **73**, 139–144.
- 32 Very recently, novel mesoporous hybrid bio-adsorbents were found as very selective materials for Th(IV): H. Goma, M. A. Shenashen, M. F. Cheira, K. Sueki, T. A. Seaf El-Nasr, M. M. Selim and S. A. El-Safty, A novel, spongy mesoporous hybrid bio-adsorbents derived from agricultural waste for highly selective thorium recovery, *J. Cleaner Prod.*, 2023, **402**, 136819.
- 33 For a comprehensive analysis of the efficiency of phosphorus ligands, see: E. Kukkonen, E. J. Virtanen and J. O. Moilanen, α -Aminophosphonates, -Phosphinates, and -Phosphine Oxides as Extraction and Precipitation Agents for Rare Earth Metals, Thorium, and Uranium: A Review, *Molecules*, 2022, **27**, 3465–3493.
- 34 X. H. Xiong, Y. Tao, Z. W. Yu, L. X. Yang, L. J. Sun, Y. L. Fan and F. Luo, Selective extraction of thorium from uranium and rare earth elements using sulfonated covalent organic framework and its membrane derivative, *Chem. Eng. J.*, 2020, **384**, 123240.
- 35 V. Venkata-Sravani, S. Sengupta, B. Sreenivasulu, G. Gopakumar, S. Tripathi, M. Chandra, C. V. S. Brahmmananda-Rao, A. Suresh and S. Nagarajan, Highly efficient functionalized MOF-LIC-1 for extraction of U(VI) and Th(IV) from aqueous solution: experimental and theoretical studies, *Dalton Trans.*, 2022, **51**, 3557–3571.
- 36 S. K. Singh and A. W. Savoy, Ionic liquids synthesis and applications: An overview, *J. Mol. Liq.*, 2020, **297**, 112038.
- 37 K. Binnemans, Lanthanides and Actinides in Ionic Liquids, *Chem. Rev.*, 2007, **107**, 2592–2614.
- 38 I. Billard, A. Ouadi and C. Gaillard, Liquid–liquid extraction of actinides, lanthanides, and fission products by use of ionic liquids: from discovery to understanding, *Anal. Bioanal. Chem.*, 2011, **400**, 1555–1566.
- 39 A. N. Turanov, V. K. Karandashev, Zh. P. Burmii and A. N. Yarkevich, Effect of Dialkylsulfosuccinate-Based Ionic-Liquids on the Extraction of Lanthanides(III), Uranium(VI), and Thorium (IV) with Diphenyl(dibutylcarbamoylmethyl)phosphine Oxide from Nitric Acid Solutions, *Russ. J. Gen. Chem.*, 2022, **92**, 418–423.
- 40 (a) Q. Wu, F. Zhang, Q.-G. Huang, X. Fu, Y. Li, X.-X. Li, Y.-N. Niu and Z.-Y. Yan, A novel one-step strategy for extraction and solidification of Th(IV) based on self-assembly driven by malonamide-based [DC18DMA]⁺ ionic liquids, *Chem. Eng. J.*, 2022, **430**(Part_1), 132717; (b) F. Zhang, Q. Wu, J.-X. Yan, Q.-G. Huang, Y. Li, X. Fu, X.-X. Li and Z.-Y. Yan, An integrated strategy for the extraction and solidification of Th(IV) ions from aqueous HNO solution based on self-assembly triggered by [DODMA] [DGA] ionic liquids, *Sep. Purif. Technol.*, 2022, **282**(Part_B), 120111.
- 41 For an effective process for the separation of U(VI) and Th(IV) from rare earth elements, see: J. Lu, K. He, Y. Wang, G. Chen, H. Weng and M. Lin, An effective process for the separation of U(VI), Th(IV) from rare earth elements by using ionic liquid Cyphos IL 104, *Chin. Chem. Lett.*, 2022, **33**, 3422–3428.
- 42 X. Xie, Z. Qin, Y. He, P. Xiong, Z. Huang, Y. Mao, H. Wei and L. Zhuo, Significant enhanced uranyl ions extraction efficiency with phosphoramidate-functionalized ionic liquids *via* synergistic effect of coordination and hydrogen bond, *Sci. Rep.*, 2017, **7**, 15735–15746.
- 43 A. Saha, K. Kumari, S. Sharma, R. Kumar, M. Sahu, R. M. R. Dumpala, M. Shafeeq PP, S. B. Deb and M. K. Saxena, Selective Extraction of Thorium(IV) from Uranium and Rare Earth Elements Using Tetraphenylethane-1,2-diylbis(phosphoramidate), *Inorg. Chem.*, 2023, **62**, 9391–9399.
- 44 A. N. Turanov, V. K. Karandashev, O. I. Artyushin and E. V. Sharova, Extraction of U(VI), Th(IV), and Lanthanides(III) from nitric acid solutions with CMPO-Functionalized ionic liquid in molecular diluents, *Solvent Extr. Ion Exch.*, 2015, **33**, 540–553.
- 45 (a) A. Sengupta, P. K. Mohapatra, M. Iqbal, J. Huskens and W. Verboom, A diglycolamide-functionalized task specific ionic liquid (TSIL) for actinide extraction: Solvent extraction, thermodynamics and radiolytic stability studies, *Sep. Purif. Technol.*, 2013, **118**, 264–270; (b) D. Ternova, A. Ouadi, V. Mazan, S. Georg, M. Boltoeva, V. Kalchenko, S. Miroshnichenko, I. Billard and C. Gaillard, New ionic liquid based on the CMPO pattern for the sequential extraction of U(VI), Am(III) and Eu(III), *J. Solution Chem.*, 2018, **47**, 1309–1325; (c) M. Paramanik, D. R. Raut, A. Sengupta, S. K. Ghosh and P. K. Mohapatra, A trialkyl phosphine oxide functionalized task specific ionic liquid for actinide ion complexation: extraction and spectroscopic studies, *RSC Adv.*, 2016, **6**, 19763–19767; (d) A. Saha, N. Tiwari, S. B. Deb and M. K. Saxena, Selective liquid-liquid



- extraction of uranium by phosphoramidate-group bearing ionic liquid, *ChemistrySelect*, 2019, **4**, 7691–7697; (e) L. Maria, A. Cruz, J. M. Carretas, B. Monteiro, C. Galinha, S. S. Gomes, M. F. Araújo, I. Paiva, J. Marçalo and J. P. Leal, Improving the selective extraction of lanthanides by using functionalized ionic liquids, *Sep. Purif. Technol.*, 2020, **237**, 116354.
- 46 Y. Zuo, J. Chena and D. Li, Reversed micellar solubilization extraction and separation of thorium(IV) from rare earth(III) by primary amine N1923 in ionic liquid, *Sep. Purif. Technol.*, 2008, **63**, 684–690.
- 47 J. Fu, Q. Chen, T. Sun and X. Shen, Extraction of Th(IV) from aqueous solution by room-temperature ionic liquids and coupled with supercritical carbon dioxide stripping, *Sep. Purif. Technol.*, 2013, **119**, 66–71.
- 48 A. Rao and B. S. Tomar, Extraction of thorium employing *N,N*-dialkyl amide into room temperature ionic liquid followed by supercritical carbon dioxide stripping, *Sep. Purif. Technol.*, 2016, **161**, 159–164.
- 49 Y. Shen, S. Wang, L. Zhu, J. Wang and W. Wu, Extraction of Th(IV) from an HNO₃ solution by diglycolamide in ionic liquids, *Ind. Eng. Chem. Res.*, 2011, **50**, 13990–13996.
- 50 H. M. Luo, R. A. Boll, J. R. Bell and S. Dai, Facile solvent extraction separation of Th-227 and Ac-225 based on room-temperature ionic liquids, *Radiochim. Acta*, 2012, **100**, 771–777. New separation methodologies for radioisotopes are crucial to many medical applications.
- 51 A. N. Turanov, V. K. Karandashev, V. A. Khvostikov, K. V. Tcarkova, E. V. Sharova, O. I. Artyushin and N. A. Bondarenko, Extraction of REE(III), U(VI), and Th(IV) with Bis[N-alkyl-N-(2-diphenylphosphinylolethyl)] diglycolamides from Nitric Acid Solutions, *Russ. J. Inorg. Chem.*, 2022, **67**, 2045–2049.
- 52 A. Sengupta, M. Singh, M. Sundarajan, L. Yuan, Y. Fang, X. Yuan and W. Feng, Understanding the extraction and complexation of thorium using structurally modified CMPO functionalized pillar[5]arenes in ionic liquid: Experimental and theoretical investigations, *Inorg. Chem. Commun.*, 2017, **75**, 33–36.
- 53 Z. Karamzadeh, M. R. Yaftian, Z. Shiri-Yekta, A. Nilchi and L. Dolatyari, Extraction-separation of Eu(III)/Th(IV) Ions with a Phosphorylated Ligand in an Ionic Liquid, *Iran. J. Chem. Chem. Eng.*, 2016, **35**, 89–95.
- 54 W. Li, S. Yang, H. Lv, Z. Liu, J. Wu, S. Li and Y. Shen, Solvent extraction of Th(IV) from aqueous solution with methylimidazole in ionic liquid, *Radiochim. Acta*, 2016, **104**, 681–690.
- 55 Z. Shiri-Yekta, M. R. Yaftian and A. Nilchi, Extraction-separation of Eu(III) and Th(IV) ions from nitrate media into a room-temperature ionic liquid, *J. Iran. Chem. Soc.*, 2013, **10**, 221–227.
- 56 P. Ren, Y. Li, Z. Wang, Y. Geng, T. Yu and R. Hua, Extraction and separation of thorium(IV) and uranium(VI) with 4-oxaheptanediamide into ionic liquid system from aqueous solution, *Chem. Pap.*, 2020, **74**, 2049–2057.
- 57 A. N. Turanov, V. K. Karandashev, A. N. Yarkevich and V. A. Khvostikov, Extraction of REE(III), U(VI), and Th(IV) from nitric acid solutions with diphenyl(dibutylcarbamoylmethyl)phosphine oxide in the presence of quaternary ammonium bis[(trifluoromethyl)sulfonyl]imides, *Radiochemistry*, 2019, **61**, 694–699.
- 58 A. N. Turanova, V. K. Karandashev and A. N. Yarkevich, Extraction of REEs(III), U(VI), and Th(IV) from nitric acid solutions with carbamoylmethylphosphine oxides in the presence of an ionic liquid, *Radiochemistry*, 2013, **55**, 382–387.
- 59 S. Annam, C. C. S. B. Rao, N. Sivaraman, A. Sivaramakrishna and K. Vijayakrishna, Carbamoylmethylphosphine oxide functionalised porous crosslinked polymers towards sequential separation of uranium (VI) and thorium (IV), *React. Funct. Polym.*, 2018, **131**, 203–210.
- 60 Y. Zhang, Z. Liu, F. Fan, L. Zhu and Y. Shen, Extraction of Uranium and Thorium from nitric acid solution by TODGA in Ionic Liquids, *Sep. Sci. Technol.*, 2014, **49**, 1895–1902.
- 61 M. Y. Alyapyshev, V. A. Babain and L. I. Tkachenko, Amides of heterocyclic carboxylic acids as novel extractants for high-level waste treatment, *Radiochemistry*, 2014, **56**, 565–574.
- 62 S. M. Ibrahim, Y. Zhang, Y. Xue, S. Yang, F. Ma and G. Tian, Extraction of Lanthanides(III) along with Thorium(IV) from chloride solutions by *N,N*-di(2-Ethylhexyl)-diglycolamic acid, *Solvent Extr. Ion Exch.*, 2020, **38**, 417–429.
- 63 R. Boyd, L. Jin, P. Nockemann, P. K. J. Robertson, L. Stella, R. Ruhela, K. R. Seddon and H. Q. N. Gunaratne, Ionic liquids tethered to a preorganized 1,2-diamide motif for extraction of lanthanides, *Green Chem.*, 2019, **21**, 2583–2588.
- 64 Y. Li, Z. Weng, Y. Wang, L. Chen, D. Sheng, Y. Liu, J. Diwu, Z. Chai, T. E. Albrecht-Schmitt and S. Wang, Centrosymmetric and chiral porous thorium organic frameworks exhibiting uncommon thorium coordination environments, *Dalton Trans.*, 2015, **44**, 20867–20873.
- 65 M. W. Rosenzweig, J. Hümmer, A. Scheurer, C. Álvarez-Lamsfus, F. W. Heinemann, L. Maron, M. Mazzanti and K. Meyer, A complete series of uranium(IV) complexes with terminal hydrochalcogenido (EH) and chalcogenido (E) ligands E = O, S, Se, Te, *Dalton Trans.*, 2019, **48**, 10853.
- 66 P. Sharma, D. R. Pahls, B. L. Ramirez, C. C. Lu and L. Gagliardi, Multiple Bonds in Uranium-Transition Metal Complexes, *Inorg. Chem.*, 2019, **58**, 10139–10147.
- 67 V. A. Cocalia, K. E. Gutowski and R. D. Rogers, The coordination chemistry of actinides in ionic liquids: A review of experiment and simulation, *Coord. Chem. Rev.*, 2006, **250**, 755–764.
- 68 J. M. Sansano, D. Lledó, G. Grindlay, M. G. Retamosa and H. Q. N. Gunaratne, *International pat.*, PCT/ES2023/070664, 2023.
- 69 V. I. Saloutin, Y. O. Edilova, Y. S. Kudyakova, Y. V. Burgart and D. N. Bazhin, Heterometallic Molecular Architectures Based on Fluorinated β -Diketone Ligands, *Molecules*, 2022, **27**, 7894–7937.
- 70 S. Benedini, Y. Zheng, A. Nitti, M. M. A. Mazza, D. Dondi, F. M. Raymo and D. Pasini, Large polarization of push-



- pull “Cruciforms” *via* coordination with lanthanide ions, *New J. Chem.*, 2022, **46**, 221–227.
- 71 J. J. Woods, R. Unnerstall, A. Hasson, D. S. Abou, V. Radchenko, D. L. J. Thorek and J. J. Wilson, Stable Chelation of the Uranyl Ion by Acyclic Hexadentate Ligands: Potential Applications for ^{230}U Targeted α -Therapy, *Inorg. Chem.*, 2022, **61**, 3337–3350.
- 72 A. C. Sather, O. B. Berryman and J. Rebek Jr, Selective Recognition and Extraction of the Uranyl Ion, *J. Am. Chem. Soc.*, 2010, **132**, 13572–13574.
- 73 C. D. Tutson and A. E. V. Gorden, Thorium coordination: A comprehensive review based on coordination number, *Coord. Chem. Rev.*, 2017, **333**, 27–43.

