

PAPER View Article Online
View Journal | View Issue



Cite this: *Phys. Chem. Chem. Phys.*, 2025, **27**, 8158

Janus group V1B-based pnictogen-halide monolayers: a new class of multifunctional quantum materials from first-principles predictions†

Sergey Gusarov,^a Chinedu E. Ekuma, ^D Gap Soo Chang,^c Mina Alizade^d and Mosayeb Naseri ^D*^{ae}

This study employed density functional theory to discover a new family of 48 two-dimensional Janus monolayers with the formula MXY, where M stands for transition metals (Cr, Mo, or W), X represents a group V element (P, As, Sb, or Bi), and Y denotes a halide (F, Cl, Br, or I). The cohesive energy and phonon dispersion calculations show that most of these materials are energetically and dynamically stable. Subsequently, the thorough investigation into the electrical structure allows the classification of these monolayers as metals (CrPl and WPI) or semiconductors with narrow band gaps ranging from 0.69 to 2.15 eV. Meanwhile, the MoSbBr, MoSbI, and WBiCl monolayers are defined to be able to function as photocatalysts in the water splitting process, and the CrAsCl monolayer exhibits significant potential for valleytronic applications due to its intrinsic valence band splitting of about 90 meV. Finally, significant Rashba splitting was observed near the Γ point in the valence band of Janus MXY monolayers, where the growth in atomic weight (W > Mo > Cr and Bi > Sb > As > P) corresponds to a greater spin-orbit coupling effect on the Rashba parameter. Their Rashba values are comparable to those ofother well-known 2D materials, indicating great potential for spintronic applications. Our findings not only present a broad range of 2D materials, but also highlight their potential for next-generation electrical, photonic, and catalytic technologies.

Received 21st October 2024, Accepted 12th March 2025

DOI: 10.1039/d4cp04036h

rsc.li/pccp

1 Introduction

Over the past two decades, global interest in graphene has surged due to its low-dimensional structure, which endows it with advantageous properties. The extraordinary characteristics of graphene have attracted the attention of both theoretical and experimental researchers, leading to the exploration of new potential 2D materials. In addition to graphene, many

metal dichalcogenides (TMDs) have emerged to be prominent figures in the research domain, owing to their multifaceted and distinctive electrical, optical, physical, chemical, and mechanical characteristics. 11 TMDs, typically represented by the formula AB2 where A denotes an element from group IV or group V transition metals and B signifies S, Se, or Te chalcogens, are typically three atoms thick. 5,12-18 Prominent examples of AB2 are the TMDs of MoSe₂, 14,15 MoS₂, 13 WS₂, 16,17 and WSe₂. 18,19 Although the reflectional symmetry along the normal direction in monolayers of TMDs makes them promising materials for use in certain domains, the absence of Rashba spin-orbit coupling (SOC) and controllable electric spin precession limits their utility in spin field-effect transistors. Additionally, the energy required to separate an exciton into its electron and hole components is quite high in 2D TMDs. As a result, photoexcited electrons and holes can rapidly recombine, which does not favor applications in light detection and harvesting. Regarding catalytic efficiency, catalysts based on TMDs have low activity because of a limited number of active edge sites. Considerable

other 2D compounds have been successfully predicted and synthesized in laboratories over the past few years. 4-10
Within the extensive array of 2D compounds, transition

^a Digital Technologies Research Centre, National Research Council Canada, 1200 Montreal Road, Ottawa, Ontario K1A0R6, Canada. E-mail: mosayeb.naseri@nrc-cnrc.gc.ca

^b Department of Physics, Lehigh University, Bethlehem, Pennsylvania 18015, USA

^c Department of Physics and Engineering Physics, University of Saskatchewan, Saskatoon, SK S7N5E2, Canada

^d Department of Materials Engineering, Science and Research Branch, Islamic Azad University, Tehran, Iran

^e Department of Chemistry, Department of Physics and Astronomy, CMS – Center for Molecular Simulation, IQST – Institute for Quantum Science and Technology, Quantum Alberta, University of Calgary, 2500 University Drive NW, Calgary, Alberta T2N 1N4, Canada. E-mail: mosayeb.naseri@ucalgary.ca

[†] Electronic supplementary information (ESI) available. See DOI: https://doi.org/10.1039/d4cp04036h

Paper

efforts have been focused on optimizing the emergence of

active edge sites or stimulating inactive basal sites; nevertheless, progress in this domain has been limited. 20,21

The structural modification of a pristine symmetric configuration provides a framework for eliciting an extensive number of intriguing features in 2D materials. Therefore, numerous approaches have been suggested to modify the symmetric structure of 2D materials to tune their fundamental properties. 22,23 In this context, the first monolayers of Janus transition metal dichalcogenides (JTMD) were studied and fabricated by two different methods in 2017.20,21 Generally, a JTMD monolayer has a formula TAB, where an atomic layer of transition metal T is located between one layer of chalcogen A and another layer of chalcogen B. Popular JTMD monolayers often comprise transition metals such as Mo and W, along with chalcogens like S, Se, and Te. This configuration results in a transformation of the space group from D_{3h} to C_v , deviating from the conventional 2H-phase TMDs. The vertical asymmetry arises from the variance in electronegativity between X and Y atoms, consequently generating an intrinsic electric field $(E_{\rm F})$. This intrinsic $E_{\rm F}$, in turn, unlocks a spectrum of additional electronic, optical, and catalytic properties, thus presenting novel prospects for future applications. Moreover, the absence of mirror symmetry unleashes novel attributes for both physical and chemical applications.

Inspired by the considerable applications of JTMD monolayers, the current study focuses on the employment of density functional theory (DFT), derived from first principles calculations, to discover a new family of Janus monolayers. There are 48 members in this family, and they have the general chemical formula MXY, where the transition metal M can be Cr or Mo, and X is one of the four pnictogens P, As, Sb, or Bi, while Y represents a halogen namely F, Cl, Br or I. For each of the designed atomic structures, its stability is estimated by considering the cohesive energy and phonon dispersion spectrum. The examination of their electronic properties, particularly their computed band gaps, reveals that these materials would predominantly be moderate band gap semiconductors, with some exhibiting narrow band gaps or metallic behavior. This characterization positions them as promising candidates for plenty of applications in the field of optoelectronics, spin-valley optoelectronics, and energy.

2 Computational details

The theoretical results were obtained by running the VASP code, 24,25 a simulation package allowing first-principles calculations using the augmented plane wave theory26 and the Perdew-Burke-Ernzerhof (PBE)²⁷ functional within the generalized gradient approximation, where the planewaves were expanded with a cut-off energy of 520 eV. Regarding the convergence, the self-consistent calculations were controlled by predetermined parameters for achieving an energy difference of 10⁻⁶ eV and an interatomic force of 0.01 eV Å^{-1} . To sample the first Brillouin zone of the designed monolayers, a k-mesh of 16 \times 16 \times 1 is utilized. During the

periodicity, two neighboring images can interact with each other affecting the computational accuracy. A 20 Å layer of vacuum was set up to eliminate this unphysical phenomenon. The PHONOPY code²⁸ was used to calculate the phonon dispersion. To treat the exchange-correlation (xc) of electrons, the PBE functional was used because it requires less computational cost to provide reliable structural and other characteristics. However, the PBE band gap is known to be significantly lower than the experimental data. Therefore, the hybrid HSE06 functional, named after the authors Heyd-Scuseria-Ernzerhof²⁹ who improved the treatment of the xc interaction, was also used to achieve more reliable band structures and band gaps.

3 Results and discussion

Table 1 summarizes the lattice parameters (a = b), bond lengths $d_1 = M-X$ and $d_2 = M-Y$ and the buckling parameter δ (measures the vertical distance between X and Y elements), which are defined in Fig. 1, for the optimized 48 MXY structures. Similar to Janus TMDs, in the crystal network of our designed 2D monolayer structure, a layer of the transition metal is located between distinct group V(X = P, As, Sb, and Bi) and group VI, i.e., halogen (Y = F, Cl, Br, and I) layers. All the designed structures show 2D Janus TMD-like atomic configurations.

Before examining the electronic properties of the designed 2D MXY structures, we need to answer the question if they are stable structures. To evaluate their stability, we first computed

their cohesive energy defined as
$$E_{\rm coh} = \frac{E_{\rm tot} - (E_{\rm M} + E_{\rm X} + E_{\rm Y})}{N_{\rm tot}}$$

 $(E_{\rm M}, E_{\rm X}, E_{\rm Y}, {\rm and}\ E_{\rm MXY}$ are the total energies of a single M atom, a single X atom, a single Y atom and the MXY monolayer unit cell, respectively). Based on our computations, all formulated 2D Janus MXY monolayers exhibit robust energetic stability, with cohesive energies spanning from -3.46 eV per atom for MoBiI to -5.09 eV per atom for CrPF and CrPBr compounds. For clarity, the calculated relative cohesive energies for the designed 2D CrXY, MoXY, and WXY structures are depicted in Fig. 2(a)–(c). The figure presents the cohesive energy trends of 2D Janus CrXY, MoXY, and WXY monolayers, highlighting their relative thermodynamic stability. In all three cases, the cohesive energy increases (becomes less negative) as we move from phosphorus (P) to bismuth (Bi), indicating that lighter pnictogens contribute to greater stability. Among the halogen substitutions, fluorine-containing monolayers exhibit the most negative cohesive energies, implying the highest stability, followed by chlorine, bromine, and iodine, which aligns with the general trend of decreasing the bond strength for heavier halogens. These trends provide essential insights into the feasibility of experimental synthesis and the potential applications of these materials in opto-electronics and catalysis.

We then assessed the dynamic stability of the designed monolayers. To evaluate this, we analyzed their phonon spectra along the path connecting the highest symmetric points in their first Brillouin zone, Γ-M-K-Γ. The dymanic stability of

Table 1 The structural parameters including the lattice constants a=b, bond lengths d_1 and d_2 , buckling parameter δ in (Å), cohesive energies $E_{\rm coh}$ (eV) and band gaps $E_{\rm g}^{\rm HSE06}$ (eV) of the predicted 2D Janus MXY monolayers. The dynamic stability criterion is determined by the phonon spectra presented in Fig. S1–S3 (ESI), where S, SU and U stand for stable, slightly unstable, and strongly unstable, respectively. HF refers to the half metallic properties

CrPF 2.86 2.05 2.33 2.87 -5.09 2.15 SU CrPCI 3.03 2.32 2.37 3.13 -4.89 1.87 SU CrPBr 3.15 2.47 2.38 3.21 -5.09 1.32 S CrPI 3.40 2.79 2.90 3.16 -4.91 HF U CrAsF 2.93 2.07 2.45 2.96 -4.86 1.84 S CrAsCI 3.10 2.32 2.49 3.21 -4.75 1.88 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbI 3.47 2.61 2.74	nic ity
CrPBr 3.15 2.47 2.38 3.21 -5.09 1.32 S CrPI 3.40 2.79 2.90 3.16 -4.91 HF U CrAsF 2.93 2.07 2.45 2.96 -4.86 1.84 S CrAsCl 3.10 2.32 2.49 3.21 -4.75 1.88 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76	
CrPI 3.40 2.79 2.90 3.16 -4.91 HF U CrAsF 2.93 2.07 2.45 2.96 -4.86 1.84 S CrAsCl 3.10 2.32 2.49 3.21 -4.75 1.88 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79	
CrAsF 2.93 2.07 2.45 2.96 -4.86 1.84 S CrAsCl 3.10 2.32 2.49 3.21 -4.75 1.88 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80<	
CrAsCl 3.10 2.32 2.49 3.21 -4.75 1.88 S CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrAsBr 3.20 2.45 2.50 3.30 -4.47 1.59 S CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrAsI 3.37 2.61 2.53 3.37 -4.17 0.97 S CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrSbF 3.09 2.10 2.66 3.09 -4.52 1.51 SU CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrSbCl 3.23 2.33 2.69 3.25 -4.56 1.56 SU CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrSbBr 3.23 2.46 2.71 3.45 -4.34 1.57 S CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrSbI 3.47 2.61 2.74 3.52 -4.07 1.34 SU CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrBiF 3.20 2.14 2.76 3.11 -4.32 1.58 SU CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrBiCl 3.31 2.35 2.79 3.39 -4.42 1.01 SU CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrBiBr 3.40 2.47 2.80 3.49 -4.23 1.18 S	
CrBiI 3.56 2.61 2.83 3.57 -4.01 0.78 S	
MoPF 3.00 2.20 2.43 3.06 -4.40 2.09 SU	
MoPCl 3.17 2.48 2.47 3.33 -4.32 0.69 SU	
MoPBr 3.26 2.62 2.47 3.41 -4.07 1.06 SU	
MoPI 3.43 2.87 2.41 3.44 -3.80 0.00 SU	
MoAsF 3.06 2.21 2.54 3.15 -4.19 1.97 SU	
MoAsCl 3.22 2.47 2.58 3.42 -4.16 2.05 SU	
MoAsBr 3.30 2.59 2.59 3.51 -3.93 1.59 SU	
MoAsI 3.43 2.74 2.61 3.59 -3.65 1.14 U	
MoSbF 3.19 2.23 2.73 3.29 -3.89 1.64 S	
MoSbCl 3.32 2.47 2.77 3.56 -3.97 1.68 SU	
MoSbBr 3.39 2.59 2.78 3.69 -3.76 1.64 SU	
MoSbI 3.52 2.73 2.81 3.76 -3.54 1.52 SU	
MoBiF 3.29 2.25 2.82 3.29 -3.70 1.60 S	
MoBiCl 3.39 2.47 2.86 3.59 -3.83 1.33 S	
MoBiBr 3.46 2.59 2.87 3.70 -3.65 1.43 U	
MoBiI 3.59 2.72 2.89 3.78 -3.46 1.33 U	
WPF 3.00 2.22 2.42 3.09 -5.05 1.93 SU	
WPCl 3.15 2.49 2.45 3.34 -4.98 1.61 S	
WPBr 3.15 2.49 2.45 3.34 -4.73 1.58 U	
WPI 3.46 2.87 2.42 3.43 -4.46 0.00 SU	
WAsF 3.04 2.23 2.53 3.19 -4.79 1.97 SU	
WASCl 3.21 2.48 2.56 3.43 -4.78 2.11 SU	
WAsBr 3.32 2.61 2.58 3.51 -4.55 1.67 U	
WASI 3.46 2.75 2.61 3.57 -4.30 1.18 U	
WSbF 3.16 2.26 2.72 3.34 -4.43 1.63 U	
WSbCl 3.32 2.47 2.77 3.56 -4.54 1.68 U	
WSbBr 3.42 2.61 2.77 3.65 -4.35 1.74 U	
WSbI 3.56 2.75 2.80 3.73 -4.16 1.65 U	
WBiF 3.27 2.28 2.81 3.36 -4.21 1.57 U	
WBiCl 3.41 2.49 2.85 3.58 -4.39 1.58 U	
WBiBr 3.49 2.61 2.86 3.69 -4.22 1.61 U	
WBiI 3.61 2.74 2.88 3.77 -4.05 1.42 U	

the MXY monolayers are reported in Table 1. It is established that 12 out of 48 studied MXY monolayers are dynamically stable as there are no imaginary modes in the phonon dispersion curves of these structures. For instance, Fig. 1(c) and (e) show the positive phonon spectra of MoBiF and MoBiCl monolayers, which are dynamically stable. There are also 21 MXY monolayers with slightly negative phonon frequencies at the Γ -point, as shown in Fig. S1S3 (ESI†). These imaginary modes may arise from the limitations of the computational model, or

the approximations used in the calculations, particularly those based on density functional theory (DFT). Moreover, they disappear when 2D structures are deposited on a suitable substrate because the substrate can effectively screen interactions that lead to negative phonon frequencies, thereby stabilizing the materials. 30,33 Strain can also effectively stabilize the 2D materials by shifting the negative phonon frequencies into the positive regime. 30-32,34 Therefore, such monolayers can also be considered as relatively stable materials. Fig. S1-S3 (ESI†) also depict the negative phonon frequencies of 15 MXY monolayers, indicating that these monolayers are not stable. The ZA, TA, and LA acoustic modes are crucial for heat conduction in narrow-gap semiconductors. ZA denotes the flexural acoustic mode, which is distinguished by atomic vibrations occurring in the z-direction. The terms LA and TA refer to the longitudinal and transverse acoustic modes, respectively. These modes involve atomic vibrations that occur within the plane of the 2D structures. Furthermore, upon examining the phonon spectra of the designed monolayers, it is evident that a significant phonon band gap is present in the spectra of MoXY and WXY monolayers. Specifically, this gap is observed in the following structures: MoPF, MoPCl, MoAsCl, MoSbCl, MoPBr, MoAsBr, MoSbBr, WPF, WPCl, WPBr, WAsF, WAsCl, and WAsBr (excluding the structures with the negative phonon frequency). A significant phonon band gap allows for the inhibition of optical phonon decay into acoustic phonons and reduces the rate at which carriers cool down.35 If there is no available path for optical phonons to convert into acoustic phonons, it is possible to sustain a population of hot optical phonons. Electrons have the ability to absorb optical phonons, which allows them to maintain a population of heated carriers. The presence of a gap in the phonon dispersion, specifically between the optical and acoustic branches, can eliminate the primary pathway for decay.³⁶ Furthermore, to elucidate the bonding nature of these monolayers, the 2D electron densities of the MoSbBr and MoSbI structures are illustrated as a reference in Fig. 1(d) and (f). Upon closer examination of these figures, it becomes apparent that, within a specific transition metal-based compound, the energetic stability decreases as the size of the X element (the group V element) increases. Additionally, for a given combination of a transition metal and a halogen element, the energetic stability diminishes with an increase in the size of the X element (the group V element).

After assessing the stability of 2D Janus MXY monolayers, we investigated their electronic properties by calculating their band structures. To obtain more accurate band gaps, we employed the HSE06 functional. The band structures of 2D Janus MXY monolayers are depicted in Fig. S4–S6 of the ESI.† The band gaps $E_{\rm g}^{\rm HSE06}$ (eV) of these monolayer materials are reported in Table 1. Our analysis reveals clear trends in the electronic properties of the monolayer systems composed of Cr, Mo, and W combined with group V elements (P, As, Sb, and Bi) and halogens (F, Cl, Br, and I). As the halogen is substituted from F to heavier elements like Cl, Br, and I, the band gap generally decreases, with several iodine-containing compounds exhibiting metallic behavior (zero band gap) compared to their

Paper


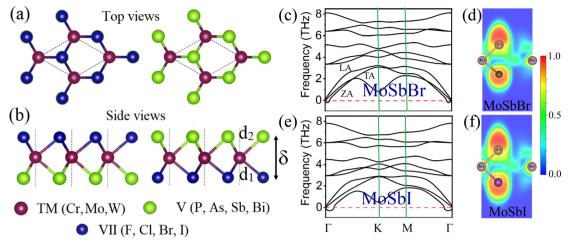


Fig. 1 Crystal structure of 2D Janus MXY monolayers from top (a) and side views (b), phonon dispersion spectra and the electron localization function of MoSbBr (c) and (d), and MoSbi (e) and (f) monolayers

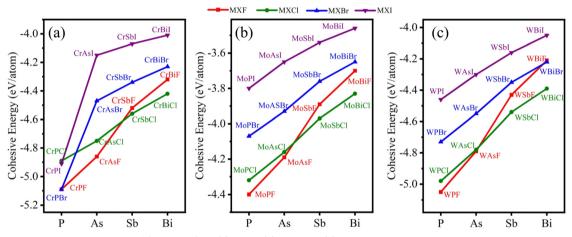

The calculated cohesive energies of 2D Janus CrXY (a), MoXY (b), and WXY (c) structures.

semiconducting fluorine analogs. This trend is attributed to the increased lattice parameters and reduced orbital overlap associated with the larger, less electronegative halogens, which in turn lowers the energy separation between the conduction and valence bands.

Moreover, variations in the group V element further modulate the band gap, generally, with heavier elements tending to yield narrower gaps due to the increasing atomic size, which weakens the orbital overlap and reduces hybridization strength. However, deviations from this trend arise in several cases. For instance, CrBiF has a slightly higher band gap than CrSbF, likely due to weaker orbital hybridization and enhanced relativistic effects in Bi-containing systems, suggesting that subtle structural distortions and differences in bond lengths play a crucial role in shaping electronic behavior. Furthermore, the transition metal component also plays a significant role: Cr-based systems tend to have higher cohesive energies and wider band gaps, while Mo- and W-based compounds show more variable electronic behaviors under similar substitutions. These insights highlight the delicate interplay between atomic size, electronegativity, and orbital hybridization in tuning the electronic properties of two-dimensional materials, offering valuable guidance for the design of novel semiconductors and conductive materials.

For CrPI, MoPI, and WPI cases, by further assessment we realized that CrPI exhibits a half-metallic ferromagnetic nature, while MoPI and WPI show metallic behavior. Specifically, for the case of 2D CrPI, which exhibits a half-metallic electronic structure and a ferromagnetic ground state, the ferromagnetic ordering inherently breaks timereversal symmetry (TRS). Consequently, the system cannot support a Z2 topological classification, as Z2 (quantum spin hall state) invariants require preserved TRS. To assess the topological nature of the material, we calculated the Chern number. The Chern number serves as a topological invariant associated with the integral of Berry curvature over the entire Brillouin zone and is a hallmark of topologically nontrivial phases such as the quantum anomalous Hall effect (QAHE). A nonzero Chern number is indicative of a nontrivial topology, typically characterized by chiral edge states and quantized Hall conductance. However, the

calculated Chern number for 2D CrPI is zero, signifying the absence of a net Berry curvature across the Brillouin zone. This result implies that the system does not exhibit any topological features associated with the QAHE or other topologically nontrivial phases. The zero Chern number indicates that Berry curvature contributions from the different regions of the Brillouin zone cancel out, leading to a topologically trivial phase. In summary, the ferromagnetic half-metallic nature of 2D CrPI, combined with its zero Chern number, confirms that the material is topologically trivial. Although its spin-polarized electronic structure and broken TRS are intriguing from a materials science perspective, they do not give rise to any topologically protected edge states or nontrivial topological order.

The observed band gap variations have significant implications for potential applications. Monolayers with moderate and tunable band gaps are promising for optoelectronics and photovoltaics, as they can absorb visible and near-infrared light efficiently. Meanwhile, metallic and narrow-gap systems are attractive for spintronics, where spin-polarized transport is crucial, and for catalytic applications, where metallic surfaces can facilitate redox reactions. The presence of an intrinsic builtin dipole due to the Janus structure enhances charge separation and could lead to improved performance in photocatalytic water splitting. The non-monotonic trends observed across different monolayers highlight the importance of external perturbations such as strain, doping, and applied electric fields in further modifying and optimizing their electronic properties.

Strain engineering, in particular, could be a key tool for transforming indirect band gaps into direct ones, thereby enhancing their optoelectronic efficiency. These findings underscore the necessity for both theoretical and experimental investigations into the tunability of Janus monolayers, ensuring their integration into next-generation electronic, optical, and catalytic technologies.

When exploring potential applications of a material, the work function (Φ) is a crucial parameter in the analysis of electronic materials, along with the band structure; therefore, we calculated Φ using the equation $\Phi = E_{\text{vac}} - E_{\text{F}}$, where E_{vac} represents the vacuum level and $E_{\rm F}$ denotes the Fermi level. These values were obtained from the electrostatic potential of the MoSbBr monolayer shown in Fig. 3(d). Due to the asymmetry in Janus materials, it is essential to consider the internal electric field resulting from the electronegativity difference between atomic layers. It is well-known that such intrinsic electric fields can enhance the separation of electron-hole pairs, beneficial for applications like photocatalytic water splitting.³⁷ To account for this monolayer, dipole corrections were incorporated into the electrostatic potential calculations for vertically asymmetric Janus monolayers.³⁸ Disrupting the vertical mirror symmetry in Janus structures leads to varying electrostatic potentials $(\Delta \Phi)$ between the bottom $(0 \ 0 \ \bar{1})$ and top (0 0 1) surfaces, as illustrated in Fig. 3(d). This variation is reflected as differences in work functions on the opposite sides of the Janus materials. Table S1 in the ESI† details the

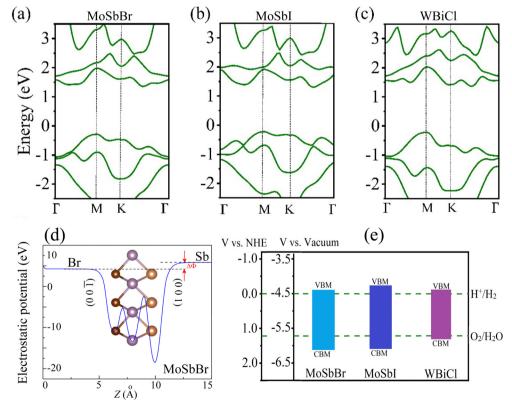


Fig. 3 The band structures of 2D Janus MoSbBr (a), MoSbI (b) and WBiCl (c) monolayers, work function of MoSbBr (d), and (e) band alignments of 2D Janus MoSbBr, MoSbI and WBiCl monolayers.

 $\Delta \Phi$ values, indicating changes in electronegativity between layers.

The moderate electrical band gap exhibited by these materials positions them as promising candidates for a variety of applications, including solar cells and water splitting. Furthermore, the inclusion of transition metals in these materials results in strong spin-orbit coupling, which could be harnessed for spin-valley optoelectronic applications. In this paper, we focus specifically on water splitting and the spin-orbit band splitting properties of these materials. The water splitting process involves two fundamental reactions: the hydrogen evolution reaction (HER) and the oxygen evolution reaction (OER); $2H^+ + 2e^- \rightarrow H_2$, $E^0 = 0.00$ eV and $2H_2O \rightarrow O_2 + 4H^+$, $E^0 =$ 1.23 eV, concluding; $H_2O \rightarrow 1/2O_2 + 2H^+$, $E^0 = 1.23$ eV. In the search for promising photocatalytic materials, the primary strategy revolves around finding materials with strong visible light absorption,³⁹ leading to the generation of electron-hole pairs that can participate in the HER and OER reactions on the catalyst surface. To achieve this objective, certain criteria must

- The material should be a semiconductor with a moderate bandgap, ideally greater than 1.23 eV.
- It should exhibit minimal recombination charge centers to ensure efficient separation and rapid transfer of photogenerated electrons and holes.
- The material's band edges must be appropriately positioned. Specifically, at pH = 0, the valence band minimum (VBM) should be lower than -5.67 eV, while the conduction band minimum (CBM) should be higher than -4.44 eV.

Considering the calculated moderate band gaps, by using Mulliken electronegativity rules, 40-42 we computed the absolute positions of the VBM and CBM that would give us an initial insight into use in water splitting applications. Based on the Mulliken electronegativity rules that are $E_{VBM} = \chi - E_{C} + 1/2E_{g}$ and $E_{\rm CBM} = \chi - E_{\rm C} - 1/2E_{\rm g}$ in which $E_{\rm g}$ is the band gap of the considered material, $E_{\rm C}$ is the energy of the free electron in the hydrogen scale (4.5 eV), χ represents the Mulliken electronegativity that can be obtained by $[\chi(A)^a \times \chi(B)^b \times \cdots \times$ $\chi(Z)^z |_{a+b+\cdots+z}^{\frac{1}{a+b+\cdots+z}}$ (a, b, ..., z are the numbers of each atom in the compound) and $E_{\rm VBM}$ and $E_{\rm CBM}$ are the energies at the VBM and CBM, respectively, and $\chi(m)=\frac{E_{ea}+E_{i}}{2}$ (E_{ea} and E_{i} refer to the electron affinity and the first ionization energy of the m element).

Utilizing the calculated band gaps, we determined the band edges for all compounds, as summarized in Table 1. Our analysis indicates that among the stable monolayer structures predicted, three structures including MoSbBr, MoSbI and WBiCl exhibit considerable potential for application in water splitting. The band edges of MoSbBr, MoSbI and WBiCl are presented in Fig. 3. It is worth noting that while the obtained band gaps and positions of the valence band maximum (VBM) and conduction band minimum (CBM) suggest promising applications of MoSbBr, MoSbI and WBiCl monolayers for water splitting, further analysis involving the calculation of the Gibbs free energy for the hydrogen evolution reaction (HER)

Table 2 The calculated band alignments E_{VBM} and E_{CBM} (eV), overpotentials χ (H₂) and χ (O₂) (eV), light absorption efficiency (η_{abs}) (%), charge carrier utilization (η_{cu}) (%) and STH efficiency (η_{STH}) (%) for MoSbBr, MoSbI, and WBiCl monolayers

	E_{CBM}	E_{CBM}	χ (H ₂)	$\chi\left(O_2\right)$	$\eta_{ m abs}$	$\eta_{ m cu}$	η_{STH}
MoSbBr MoSbI WBiCl		-6.00 -5.94 -6.01	0.08 0.02 0.01	0.33 0.27 0.34	54.32 60.53 57.20	37.84 37.22 39.87	14.87 14.42 19.83


and oxygen evolution reaction (OER) is essential for accurately assessing the photocatalytic water splitting potential. Moreover, considering the calculated band gaps and absolute band edge positions, a detailed study of strain effects on the electronic, optical and water splitting properties of these materials is suggested.41,43,44

The efficiency of solar energy conversion into hydrogen is a critical qualitative metric for solar energy water splitting photocatalysts. The calculated solar-to-hydrogen (STH) efficiency is high (see Discussion S1 for more information, ESI†). Table 2 lists the overpotentials for the hydrogen and oxygen evolution reactions χ (H₂) and χ (O₂), as well as the efficiency of light absorption (η_{abs}) and carrier utilisation (η_{cu}) for MoSbBr, MoSbI, and WBiCl monolayers (refer to the ESI†). The light absorption efficiency (η_{abs}) of the MoSbBr, MoSbI, and WBiCl monolayers exceeds 50% and is significantly dependent on the band gap value. Furthermore, the optimum levels of γ (H₂) and χ (O₂) result in energy conversion efficiencies of carrier utilization (η_{cu}) that exceed 35%. The high efficiencies of η_{abs} and η_{cu} result in a high STH efficiency (η_{STH}). The η_{STH} of these monolayers exceeds 10%, surpassing that of pentagonal PdSe₂ (12.59%), 45 GeN₃ (12.63%), 46 Janus WSSe (11.7%), 47 β-Te₂S and β-Te₂Se (13.46% and 12.09%),⁴⁸ Ge₂Se₂P₄ (12.334%),⁴⁹ and $NbOX_2$ (X = Cl, Br, and I) monolayers (14.11-17.05%).⁵⁰ As a result, we believe that the Janus MoSbBr, MoSbI, and WBiCl monolayers reach the essential value for affordable hydrogen production by photocatalysis (over 10%).

The 2D Janus MXY monolayer structures, similar to the 2D Janus TMDs (MXY), have a asymmetric structure with a C_{3v} point group. This is in contrast to the single-layer MX₂ TMD structure, which has a higher symmetry of the D_{3h} point group. 51,52 The asymmetrical configuration of the crystal structure of these Janus 2D materials creates a fundamental electric field, resulting in the separation of spin and valley states, as well as the Rashba effect when paired with spin-orbit coupling (SOC). In modern times, spin and valley are seen as additional degrees of freedom that are apart from the electronic charge. They offer a fascinating opportunity in the field of semiconductor devices. 53,54 The combination of spin-orbit coupling (SOC) and a break of inversion symmetry in Janus TMDs leads to the occurrence of Zeeman-type spin splitting at the corners of the 2D Brillouin zone.

In order to study the spin valley splitting effect, we did an examination specifically focusing on the band structure of the 2D Janus CrAsCl monolayer. We used the PBE + SOC level of theory as a reference for our analysis. Significantly, it is noted

that although the predicted band gap values may differ, all other band characteristics stay constant irrespective of the chosen functional. The utilization of the HSE06 approach results in an enlargement of the band gap, primarily due to the inclusion of the precise exchange interaction. Therefore, employing the PBE + SOC level of theory offers useful insights into the spin valley splitting in the suggested monolayers. Fig. 4(a) and (b) illustrate the band structure of the CrAsCl monolayer, which was determined using the PBE level of theory. The first figure shows the band structure without taking spin-orbit coupling (SOC) into account, while the second figure includes the effects of SOC. The image clearly demonstrates that the monolayer CrAsCl displays characteristics of a semiconductor with an indirect (quasi-direct) bandgap. The valence band maximum (VBM) and conduction band minimum (CBM) are located at the K/K' point and somewhere along the K/K'- Γ route, respectively. When the SOC is included, Fig. 4(b) and (c) demonstrate that spin-orbit coupling mostly causes the separation of spins inside degenerate bands. This event occurs due to the violation of inversion symmetry, which causes the spin degeneracy to be disrupted at each generic k-point. Although time-reversal symmetry is maintained, the spin polarization at the K and K' locations exhibit different orientations due to the time-reversal operation that links these sites. Furthermore, features that display anomalous behavior when subjected to the time-reversal operation will have contrasting characteristics at the K and K' points. These data show the existence of a separate valley degree of freedom, therefore validating the long-

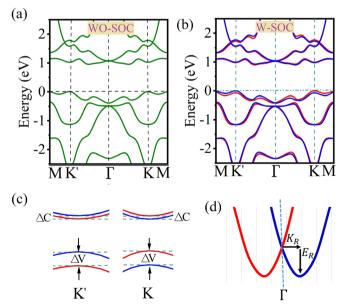

desired valley polarization. In this context, valley polarization is

Fig. 4 Band structure of the CrAsCl monolayer calculated by the PBE level of theory without spin-orbit coupling (a), band structure of the CrAsCl monolayer calculated by the PBE level of theory with spin-orbit coupling (b), schematic of valley selective excitation in which the red and blue colors denote the spin-up and spin-down states, respectively (c), and the schematic diagram of Rashba spin-splitting around the Γ point in the valence band (d)

represented as $\Delta V = E_{K'} - E_{K}$, where it represents the disparity in energy between the highest point of the valence band at K and K' valleys. According to our calculations, activating the spin-orbit coupling (SOC) causes the spin degeneracy to be removed, resulting in a decrease in the band gap from 0.95 to 0.92 eV. Significantly, a valley spin splitting of 67 meV occurs near the valence band edge due to the pronounced influence of the strong spin-orbit coupling (SOC). The conduction band edges have a negligible valley spin splitting (10 meV) in comparison to the valence band. This is related to the dominance of distinct orbitals at the valence and conduction band edges.

In addition, the disruption of mirror symmetry in Janus materials can induce Rashba spin splitting phenomena.

Table 3 The valley spin splitting energy ΔV , ΔC (eV), Rashba energy E_R (eV), momentum offset K_R (Å⁻¹), and Rashba constant α_R (eV Å)

CrPF 0.0559 0.0043 0.0026 0.0367 0.1417 CrPCI 0.059 0.004 0.0007 0.0208 0.0673 CrPBr 0.0737 0.0088 0.0005 0.0201 0.0498 CrPI — — — — — CrASF 0.068 0.018 0.0055 0.0475 0.2316 CrASCI 0.073 0.015 0.0055 0.0475 0.2316 CrASBT 0.083 0.018 0.0027 0.0341 0.158 CrASI 0.093 0.019 0.0017 0.025 0.136 CrSbI — — — — — CrSbI 0.0984 0.026 0.0022 0.0379 0.1161 CrBIF — — — — — CrBIF — — — — — CrBIF — — — — — CrBIF — —	Monolayer	ΔV	ΔC	$E_{ m R}$	$K_{ m R}$	$\alpha_{\mathbf{R}}$
CrPBr CrPI 0.0737 0.0088 0.0005 0.0201 0.0498 CrPI — — — — — CrAsF 0.068 0.018 0.0065 0.0715 0.2316 CrAsBr 0.083 0.018 0.0027 0.0341 0.1584 CrAsI 0.093 0.019 0.0017 0.025 0.136 CrSbF — — — — — CrSbCl 0.0932 0.0257 0.0025 0.0716 0.0698 CrSbBr 0.0984 0.026 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiI 0.1046 0.0479 0.0109 0.0946 0.2304 MoPP 0.1005 0.0246 0.0015 0.021 0.1429 MoPP 0.136 0.0129 0.0009 0.0194 0.0928	CrPF	0.0559	0.0043	0.0026	0.0367	0.1417
CrPI —	CrPCl	0.059	0.004	0.0007	0.0208	0.0673
CrAsF 0.068 0.018 0.0065 0.0718 0.1811 CrAsCl 0.073 0.015 0.0055 0.0475 0.2316 CrAsBr 0.083 0.018 0.0027 0.0341 0.1584 CrAsI 0.093 0.019 0.0017 0.025 0.136 CrSbF — — — — — CrSbCl 0.0932 0.0257 0.0025 0.0716 0.0698 CrSbBr 0.0984 0.026 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiI — — — — — CrBiI — — — — — CrBiIB — — — — — — CrBiIB — — — — — — — — —	CrPBr	0.0737	0.0088	0.0005	0.0201	0.0498
Crascl 0.073 0.015 0.0055 0.0475 0.2316 Crasbr 0.083 0.018 0.0027 0.0341 0.1584 Crasl 0.093 0.019 0.0017 0.025 0.136 CrSbF — — — — — CrSbCl 0.0932 0.0257 0.0025 0.0716 0.0698 CrSbBr 0.0984 0.026 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiCl — — — — — CrBiBr — — — — — CrBiBr — — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPCl 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPBr <	CrPI	_	_	_	_	_
CrAsBr 0.083 0.018 0.0027 0.0341 0.1584 CrAsI 0.093 0.019 0.0017 0.025 0.136 CrSbF — — — — — CrSbGI 0.0932 0.0257 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiRI — — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPBr 0.136 0.0129 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0007 0.0133 0.1053 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsBr 0.	CrAsF	0.068	0.018	0.0065	0.0718	0.1811
CrAsI CrSbF 0.093 0.019 0.0017 0.025 0.136 CrSbF — — — — — CrSbBCI 0.0932 0.0257 0.0025 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiBI — — — — — CrBiBr 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPBr 0.136 0.0129 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPBr 0.138 0.0282	CrAsCl	0.073	0.015	0.0055	0.0475	0.2316
CrSbF — <td>CrAsBr</td> <td>0.083</td> <td>0.018</td> <td>0.0027</td> <td>0.0341</td> <td>0.1584</td>	CrAsBr	0.083	0.018	0.0027	0.0341	0.1584
CrSbCl 0.0932 0.0257 0.0025 0.0716 0.0698 CrSbBr 0.0984 0.026 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiBr — — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCI 0.1134 0.0054 0.0007 0.0133 0.1032 MoPP 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 <	CrAsI	0.093	0.019	0.0017	0.025	0.136
CrSbBr 0.0984 0.026 0.0022 0.0379 0.1161 CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiCl — — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCl 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 <	CrSbF	_	_	_	_	_
CrSbI 0.1045 0.0232 0.0075 0.0544 0.2757 CrBiF — — — — — CrBiCl — — — — — CrBiBr — — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCl 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPBr 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsCl 0.1322 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702	CrSbCl	0.0932	0.0257	0.0025	0.0716	0.0698
CrBiFC — — — — CrBiCl — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCl 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbGI 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSiF 0.1897	CrSbBr	0.0984	0.026	0.0022	0.0379	0.1161
CrBiCl — — — — CrBiBr — — — — CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCI 0.1134 0.0054 0.0009 0.0193 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCI 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbGI 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 <td>CrSbI</td> <td>0.1045</td> <td>0.0232</td> <td>0.0075</td> <td>0.0544</td> <td>0.2757</td>	CrSbI	0.1045	0.0232	0.0075	0.0544	0.2757
CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCI 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCI 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCI 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418	CrBiF	_	_	_	_	
CrBiI 0.1446 0.0479 0.0109 0.0946 0.2304 MoPF 0.1005 0.0246 0.0015 0.021 0.1429 MoPCI 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbGI 0.1649 0.0332 0.011 0.0634 0.347 MoSbI 0.1897 0.0385 0.0115 0.0496 0.4637 MoBiF 0.1902 0.1541 0.0077 0.0511	CrBiCl	_	_	_	_	
MOPF 0.1005 0.0246 0.0015 0.021 0.1429 MOPCI 0.1134 0.0054 0.0007 0.0133 0.1053 MOPBr 0.136 0.0129 0.0009 0.0194 0.0928 MOPI — — — — — MOASF 0.1162 0.0388 0.0282 0.0756 0.746 MOASCI 0.1322 0.0193 0.0063 0.0327 0.3853 MOASBr 0.1502 0.0251 0.0041 0.0255 0.3216 MOASI 0.165 0.0302 0.0031 0.0246 0.252 MOSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCI 0.1649 0.0332 0.011 0.0634 0.347 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiGI 0.2481 0.1204 0.0046 0.031	CrBiBr	_	_	_	_	
MoPCI 0.1134 0.0054 0.0007 0.0133 0.1053 MoPBr 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoASF 0.1162 0.0388 0.0282 0.0756 0.746 MoASCI 0.1322 0.0193 0.0063 0.0327 0.3853 MoASBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoASBr 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCI 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3306 MoBiB 0.2481 0.1204 0.0046 0.031	CrBiI	0.1446	0.0479	0.0109	0.0946	0.2304
MoPBr MoPI 0.136 0.0129 0.0009 0.0194 0.0928 MoPI — — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3306 MoBiR 0.2481 0.1204 0.0046 0.031 0.2968 MoBiR 0.2524 0.1132 0.002 0.0121<	MoPF	0.1005	0.0246	0.0015	0.021	0.1429
MoPI — — — — MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiI 0.2524 0.1132 0.002 0.0121 0.3306 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 WPF 0.262 0.1011 0.0157 0.0631 0.4976 </td <td>MoPCl</td> <td>0.1134</td> <td>0.0054</td> <td>0.0007</td> <td>0.0133</td> <td>0.1053</td>	MoPCl	0.1134	0.0054	0.0007	0.0133	0.1053
MoAsF 0.1162 0.0388 0.0282 0.0756 0.746 MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiBr 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 WPF 0.262 0.1011 0.0157	MoPBr	0.136	0.0129	0.0009	0.0194	0.0928
MoAsCl 0.1322 0.0193 0.0063 0.0327 0.3853 MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiBr 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157	MoPI	_	_	_	_	
MoAsBr 0.1502 0.0251 0.0041 0.0255 0.3216 MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0077 0.0511 0.301 MoBiBr 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPBr 0.3069 0.0389 0.0081	MoAsF	0.1162	0.0388	0.0282	0.0756	0.746
MoAsI 0.165 0.0302 0.0031 0.0246 0.252 MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiF 0.1902 0.1541 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — <td< td=""><td>MoAsCl</td><td>0.1322</td><td>0.0193</td><td>0.0063</td><td>0.0327</td><td>0.3853</td></td<>	MoAsCl	0.1322	0.0193	0.0063	0.0327	0.3853
MoSbF 0.1388 0.0359 0.0107 0.0792 0.2702 MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiGI 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2524 0.1132 0.002 0.0121 0.3306 MOFF 0.262 0.1011 0.0157 0.0631 0.4976 WPCI 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAscI 0.3255 0.0383 0.0325 0.0788	MoAsBr	0.1502	0.0251	0.0041	0.0255	0.3216
MoSbCl 0.1649 0.0332 0.011 0.0634 0.347 MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiCl 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.	MoAsI	0.165	0.0302	0.0031	0.0246	0.252
MoSbBr 0.1774 0.0355 0.0115 0.0496 0.4637 MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiCI 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCI 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.25 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsI 0.3463 0.0095 0.016 0.0571 0.56	MoSbF	0.1388	0.0359	0.0107	0.0792	0.2702
MoSbI 0.1897 0.0385 0.0164 0.0418 0.7847 MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiCl 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsI 0.3463 0.0095 0.016 0.0571 0.5604 WSbF 0.3133 0.1746 0.0424 0.1529 0.554	MoSbCl	0.1649	0.0332	0.011	0.0634	0.347
MoBiF 0.1902 0.1541 0.0077 0.0511 0.3014 MoBiCl 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562	MoSbBr	0.1774	0.0355	0.0115	0.0496	0.4637
MoBiCl 0.2481 0.1204 0.0046 0.031 0.2968 MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WAsI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835<	MoSbI	0.1897	0.0385	0.0164	0.0418	0.7847
MoBiBr 0.2524 0.1132 0.002 0.0121 0.3306 MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsI 0.3463 0.0095 0.016 0.0571 0.5604 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609	MoBiF	0.1902	0.1541	0.0077	0.0511	0.3014
MoBiI 0.2535 0.0962 0.0149 0.041 0.7268 WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCl 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WASI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbGl 0.3788 0.084 0.0356 0.1267 0.562 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353	MoBiCl	0.2481	0.1204	0.0046	0.031	0.2968
WPF 0.262 0.1011 0.0157 0.0631 0.4976 WPCI 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCI 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCI 0.3788 0.084 0.0424 0.1529 0.582 WSbBr 0.3994 0.0563 0.042 0.12267 0.562 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 <td>MoBiBr</td> <td>0.2524</td> <td>0.1132</td> <td>0.002</td> <td>0.0121</td> <td>0.3306</td>	MoBiBr	0.2524	0.1132	0.002	0.0121	0.3306
WPCI 0.2876 0.0049 0.005 0.04 0.25 WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCI 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCI 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743 <td>MoBiI</td> <td>0.2535</td> <td>0.0962</td> <td>0.0149</td> <td>0.041</td> <td>0.7268</td>	MoBiI	0.2535	0.0962	0.0149	0.041	0.7268
WPBr 0.3069 0.0389 0.0081 0.04 0.405 WPI — — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WSbI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.5622 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4	WPF	0.262	0.1011	0.0157	0.0631	0.4976
WPI — — — — WAsF 0.2837 0.0534 0.0578 0.1312 0.8811 WAsCl 0.3255 0.0383 0.0325 0.0788 0.8249 WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WAsI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WPCl	0.2876	0.0049	0.005	0.04	0.25
WASF 0.2837 0.0534 0.0578 0.1312 0.8811 WASCI 0.3255 0.0383 0.0325 0.0788 0.8249 WASBr 0.3463 0.0095 0.016 0.0571 0.5604 WASI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCI 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WPBr	0.3069	0.0389	0.0081	0.04	0.405
WASCI 0.3255 0.0383 0.0325 0.0788 0.8249 WASBr 0.3463 0.0095 0.016 0.0571 0.5604 WASI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCI 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WPI	_	_	_	_	_
WAsBr 0.3463 0.0095 0.016 0.0571 0.5604 WAsI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WAsF	0.2837	0.0534	0.0578	0.1312	0.8811
WASI 0.3422 0.0059 0.0141 0.0607 0.4646 WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WAsCl	0.3255	0.0383	0.0325	0.0788	0.8249
WSbF 0.3133 0.1746 0.0424 0.1529 0.5546 WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WAsBr	0.3463	0.0095	0.016	0.0571	0.5604
WSbCl 0.3788 0.084 0.0356 0.1267 0.562 WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WAsI	0.3422	0.0059	0.0141	0.0607	0.4646
WSbBr 0.3994 0.0563 0.042 0.1229 0.6835 WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WSbF	0.3133	0.1746	0.0424	0.1529	0.5546
WSbI 0.3958 0.0388 0.0339 0.0828 0.8188 WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WSbCl	0.3788	0.084	0.0356	0.1267	0.562
WBiF 0.3701 0.005 0.0412 0.1353 0.609 WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WSbBr	0.3994	0.0563	0.042	0.1229	0.6835
WBiCl 0.4518 0.0113 0.0313 0.1234 0.5073 WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WSbI	0.3958	0.0388	0.0339	0.0828	0.8188
WBiBr 0.4643 0.0205 0.03 0.1265 0.4743	WBiF	0.3701	0.005	0.0412	0.1353	0.609
	WBiCl	0.4518	0.0113	0.0313	0.1234	0.5073
WBiI 0.4533 0.0295 0.0332 0.105 0.6324	WBiBr	0.4643	0.0205	0.03	0.1265	0.4743
	WBiI	0.4533	0.0295	0.0332	0.105	0.6324

PCCP Paper

This phenomenon arises from an internal electric field that is oriented perpendicular to the material. The electric field is created by the difference in electronegativity between the atomic layers of Janus structures, those are such materials that are based on transition metal dichalcogenides.⁵⁵ We can see a significant Rashba splitting at the Γ point in the valence band of Janus MXY monolayers, as shown in Fig. 4(d). The intensity of the Rashba spin-orbit coupling splitting is determined by three parameters: the Rashba energy (E_R) , the momentum offset (K_R) , and the Rashba constant (α_R) . The values of E_R and K_R are obtained from the band structures, $^{56-58}$ and the Rashba constant α_R is calculated using the formula $\alpha_R = 2E_R/K_R$. The Rashba-type spin splitting at the Γ point is shown schematically in Fig. 4(d). Table 3 displays the calculated values of ΔV , ΔC , E_R , K_R , and α_R for the 2D Janus MXY family. The splitting pattern follows the trend of increasing atomic weights, with SOC having a greater influence on elements like as W > Mo > Cr and Bi > Sb > As > P.

The computed Rashba parameters α_R are as follows: for CrXY, they range from 0.0498 to 0.2757 (eV Å); for MoXY, from 0.0928 to 0.7460 (eV Å); and for WXY, from 0.2500 to 0.8811 (eV Å). The α_R value for 2D Janus MXY is comparable to those of (Mo and W) X_2 (X = S and Se) (0.14-0.26 eV Å), ⁵⁹ traditional TMDs (0.05-0.40 eV Å), 55 MoSSe (0.53 eV Å), WSSe (0.72 eV Å), WSeTe (0.92 eV Å), 60 ZrS₂Se (0.717 eV Å) and HfS₂Se (0.566 eV Å), 61 SnSTe (0.755 eV Å) and SnSeTe (0.273 eV Å), 62 CrSTe (0.31 eV Å), 63 and WSiAs₃H (0.675 eV Å). 57

4 Conclusion

First principles calculations based on density functional theory were performed to discover a diverse family of 48 2D Janus MoS₂-like monolayers with the formula MXY. Many of these monolayers exhibit both energetic and dynamic stability, confirmed by their cohesive energy and phonon dispersion calculations. Most of the monolayers are semiconductors with moderate band gaps, making them promising for optoelectronic applications like solar cells and water splitting. The MoSbBr, MoSbI, and WBiCl monolayers show notable potential for water splitting due to their band structures. The inclusion of transition metals in the MXY monolayer is accompanied by a strong spin-orbit coupling effect, opening possibilities for spin-valley optoelectronics. The analysis of the electronic features reveals the quasi-direct band gap in some monolayers, which raises the necessity for a detailed band structure study. Spin-valley splitting was observed in CrAsCl monolayers. Rashba spin splitting occurs due to internal electric fields caused by the differing electronegativity of atomic layers. Rashba splitting near the Γ point in Janus MXY monolayers follows the trend W > Mo > Cr and Bi > Sb > As > P, with computed Rashba parameters ranging from 0.0498 to 0.8811 (eV Å), depending on the elements involved. Overall, this family of 2D Janus materials holds significant promise for future electronic, photonic, and catalytic technologies. Further experimental validation and research into the strain effects and catalytic performance will be essential for realizing their full potential.

Data availability

The data that support the findings of this study are available from the corresponding author upon reasonable request.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

This work was supported by the National Research Council of Canada through the Artificial Intelligence for Design program and Applied Quantum Computing (AQC) Program, and by the Natural Sciences and Engineering Research Council of Canada. The authors also acknowledge financial support from Defense Research and Development Canada (DRDC). C. E. E. acknowledges support from the U.S. National Science Foundation under Award No. DMR-2202101. The authors thank Dr. Tuan V. Vu and Dr. A. I. Kartamyshev (Van Lang University) for their valuable discussions during the development of this work.

References

- 1 K. S. Novoselov, A. K. Geim, S. V. Morozov, D.-E. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, Science, 2004, 306, 666-669.
- 2 M. J. Allen, V. C. Tung and R. B. Kaner, Chem. Rev., 2010, 110, 132-145.
- 3 C. Soldano, A. Mahmood and E. Dujardin, Carbon, 2010, 48, 2127-2150.
- 4 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, Nat. Nanotechnol., 2011, 6, 147-150.
- 5 Q. H. Wang, K. Kalantar-Zadeh, A. Kis, J. N. Coleman and M. S. Strano, Nat. Nanotechnol., 2012, 7, 699-712.
- 6 S. Z. Butler, S. M. Hollen, L. Cao, Y. Cui, J. A. Gupta, H. R. Gutiérrez, T. F. Heinz, S. S. Hong, J. Huang and A. F. Ismach, et al., ACS Nano, 2013, 7, 2898-2926.
- 7 H. Liu, A. T. Neal, Z. Zhu, Z. Luo, X. Xu, D. Tománek and P. D. Ye, ACS Nano, 2014, 8, 4033-4041.
- 8 B. Anasori, M. R. Lukatskaya and Y. Gogotsi, MXenes, Jenny Stanford Publishing, 2023, pp. 677-722.
- 9 S. Manzeli, D. Ovchinnikov, D. Pasquier, O. V. Yazyev and A. Kis, Nat. Rev. Mater., 2017, 2, 1-15.
- 10 X. Liu, Q. Li, Q. Ruan, M. S. Rahn, B. I. Yakobson and M. C. Hersam, Nat. Mater., 2022, 21, 35-40.
- 11 M. Chhowalla, H. S. Shin, G. Eda, L.-J. Li, K. P. Loh and H. Zhang, Nat. Chem., 2013, 5, 263-275.
- 12 J. A. Wilson, F. Di Salvo and S. Mahajan, Adv. Phys., 1975, 24, 117-201.
- 13 J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou and Y. Xie, Adv. Mater., 2013, 5807-5813.
- 14 Y. Shi, C. Hua, B. Li, X. Fang, C. Yao, Y. Zhang, Y.-S. Hu, Z. Wang, L. Chen and D. Zhao, et al., Adv. Funct. Mater., 2013, 23, 1832-1838.

- 15 O. Lehtinen, H.-P. Komsa, A. Pulkin, M. B. Whitwick, M.-W. Chen, T. Lehnert, M. J. Mohn, O. V. Yazyev, A. Kis and U. Kaiser, et al., ACS Nano, 2015, 9, 3274-3283.
- 16 L. Cheng, W. Huang, Q. Gong, C. Liu, Z. Liu, Y. Li and H. Dai, Angew. Chem., Int. Ed., 2014, 53, 7860-7863.
- 17 D. Braga, I. Gutiérrez Lezama, H. Berger and A. F. Morpurgo, Nano Lett., 2012, 12, 5218-5223.
- 18 W. Zhao, Z. Ghorannevis, L. Chu, M. Toh, C. Kloc, P.-H. Tan and G. Eda, ACS Nano, 2013, 7, 791-797.
- 19 J.-K. Huang, J. Pu, C.-L. Hsu, M.-H. Chiu, Z.-Y. Juang, Y.-H. Chang, W.-H. Chang, Y. Iwasa, T. Takenobu and L.-J. Li, ACS Nano, 2014, 8, 923-930.
- 20 A.-Y. Lu, H. Zhu, J. Xiao, C.-P. Chuu, Y. Han, M.-H. Chiu, C.-C. Cheng, C.-W. Yang, K.-H. Wei and Y. Yang, et al., Nat. Nanotechnol., 2017, 12, 744-749.
- 21 J. Zhang, S. Jia, I. Kholmanov, L. Dong, D. Er, W. Chen, H. Guo, Z. Jin, V. B. Shenoy and L. Shi, et al., ACS Nano, 2017, 11, 8192-8198.
- 22 L. Du, T. Hasan, A. Castellanos-Gomez, G.-B. Liu, Y. Yao, C. N. Lau and Z. Sun, Nat. Rev. Phys., 2021, 3, 193-206.
- 23 G. Scuri, T. I. Andersen, Y. Zhou, D. S. Wild, J. Sung, R. J. Gelly, D. Bérubé, H. Heo, L. Shao and A. Y. Joe, et al., Phys. Rev. Lett., 2020, 124, 217403.
- 24 G. Kresse and J. Furthmüller, Phys. Rev. B:Condens. Matter Mater. Phys., 1996, 54, 11169.
- 25 G. Kresse and J. Furthmüller, Comput. Mater. Sci., 1996, 6, 15-50.
- 26 P. E. Blöchl, Phys. Rev. B:Condens. Matter Mater. Phys., 1994, **50**, 17953.
- 27 J. P. Perdew, K. Burke and M. Ernzerhof, Phys. Rev. Lett., 1996, 77, 3865.
- 28 A. Togo and I. Tanaka, Scr. Mater., 2015, 108, 1-5.
- 29 A. V. Krukau, O. A. Vydrov, A. F. Izmaylov and G. E. Scuseria, J. Chem. Phys., 2006, 125, 224106.
- 30 W. Zhong and D. Vanderbilt, *Phys. Rev. Lett.*, 1995, 74, 2587.
- 31 X.-P. Li and D. Vanderbilt, Phys. Rev. Lett., 1992, 69, 2543.
- 32 H. Zheng, X.-B. Li, N.-K. Chen, S.-Y. Xie, W. Q. Tian, Y. Chen, H. Xia, S. Zhang and H.-B. Sun, Phys. Rev. B:Condens. Matter Mater. Phys., 2015, 92, 115307.
- 33 A. Furrer and W. Hälg, *Phys. Status Solidi B*, 1970, **42**, 821–833.
- 34 R. Maiti, C. Patil, M. Saadi, T. Xie, J. Azadani, B. Uluutku, R. Amin, A. Briggs, M. Miscuglio and D. Van Thourhout, et al., Nat. Photonics, 2020, 14, 578-584.
- 35 P. Blaha, K. Schwarz, G. Madsen, D. Kvasnicka, J. Luitz and K. Schwarz, An Augmented PlaneWave+ Local Orbitals Program for Calculating Crystal Properties, revised edition, WIEN2k 13.1 (Release 06/26/2013), Wien2K Users Guide, Isbn 3-9501031-1 9501031-2 technical report, 2008.
- 36 G. Conibeer, D. König, M. Green and J. Guillemoles, Thin Solid Films, 2008, 516, 6948-6953.

- 37 Z. Cheng, Z. Hu, X. Ma, M. Wang, N. Gan and M. Pan, J. Phys. Chem. C, 2022, 126, 11510-11517.
- 38 L. Bengtsson, Phys. Rev. B:Condens. Matter Mater. Phys., 1999, 59, 12301.
- 39 Z. Cheng, Z. Hu, Z. Liu, C. Han, M. Wang, J. He, W. Zou and X. Ma, Surf. Interfaces, 2022, 31, 102082.
- 40 R. S. Mulliken, J. Chem. Phys., 1934, 2, 782-793.
- 41 M. Naseri, J. Phys. Chem. C, 2023, 127, 1687-1696.
- 42 D. D. Vo, T. V. Vu, A. Kartamyshev, T. H. Ho and N. N. Hieu, Nanoscale Adv., 2024, 6, 6019-6028.
- 43 M. Naseri, D. R. Salahub, T. V. Vu and H. Zakaryae, J. Mater. Chem. C, 2022, 10, 11424.
- 44 A. Bafekry, M. Naseri, M. Faraji, M. Fadlallah, D. Hoat, H. Jappor, M. Ghergherehchi, D. Gogova and H. Afarideh, Sci. Rep., 2022, 12, 22269.
- 45 C. Long, Y. Liang, H. Jin, B. Huang and Y. Dai, ACS Appl. Energy Mater., 2018, 2, 513-520.
- 46 J. Liu, Y. Shen, X. Gao, L. Lv, Y. Ma, S. Wu, X. Wang and Z. Zhou, Appl. Catal., B, 2020, 279, 119368.
- 47 L. Ju, M. Bie, X. Tang, J. Shang and L. Kou, ACS Appl. Mater. Interfaces, 2020, 12, 29335-29343.
- 48 J. Singh and A. Kumar, J. Mater. Chem. C, 2023, 11, 1173-1183.
- 49 T. V. Vu, N. N. Hieu, D. D. Vo, A. Kartamyshev, H. D. Tong, T. T. Trinh, V. Khuong Dien, Z. Haman, P. Dey and N. Khossossi, J. Phys. Chem. C, 2024, 128, 4245-4257.
- 50 L. Pan, Y.-L. Wan, Z.-Q. Wang, H.-Y. Geng and X.-R. Chen, J. Appl. Phys., 2023, 134, 085105.
- 51 L. Dong, J. Lou and V. B. Shenoy, ACS Nano, 2017, 11, 8242-8248.
- 52 R. Li, Y. Cheng and W. Huang, Small, 2018, 14, 1802091.
- 53 M. Abdollahi and M. B. Tagani, J. Mater. Chem. C, 2020, 8, 13286-13296.
- 54 D. Xiao, G.-B. Liu, W. Feng, X. Xu and W. Yao, Phys. Rev. Lett., 2012, 108, 196802.
- 55 T. Hu, F. Jia, G. Zhao, J. Wu, A. Stroppa and W. Ren, Phys. Rev. B, 2018, 97, 235404.
- 56 S. Singh and A. H. Romero, Phys. Rev. B, 2017, 95, 165444.
- 57 T. V. Vu, B. D. Hoi, A. Kartamyshev and N. N. Hieu, J. Appl. Phys., 2024, 135, 074301.
- 58 T. V. Vu, N. P. Anh, H. V. Phuc, A. Kartamyshev and N. N. Hieu, New J. Chem., 2023, 47, 11660-11668.
- 59 X. Li, S. Zhang, H. Huang, L. Hu, F. Liu and Q. Wang, Nano Lett., 2019, 19, 6005-6012.
- 60 J. Chen, K. Wu, W. Hu and J. Yang, J. Am. Chem. Soc., 2022, 144, 20035-20046.
- 61 R. Ahammed, N. Jena, A. Rawat, M. K. Mohanta, Dimple and A. De Sarkar, J. Phys. Chem. C, 2020, 124, 21250-21260.
- 62 B. D. Bhat, J. Phys.: Condens. Matter, 2023, 35, 435301.
- 63 S. Chen, Z. Zeng, B. Lv, S. Guo, X. Chen and H. Geng, Phys. Rev. B, 2022, 106, 115307.