


# PCCP

Physical Chemistry Chemical Physics

rsc.li/pccp

25  
YEARS  
ANNIVERSARY

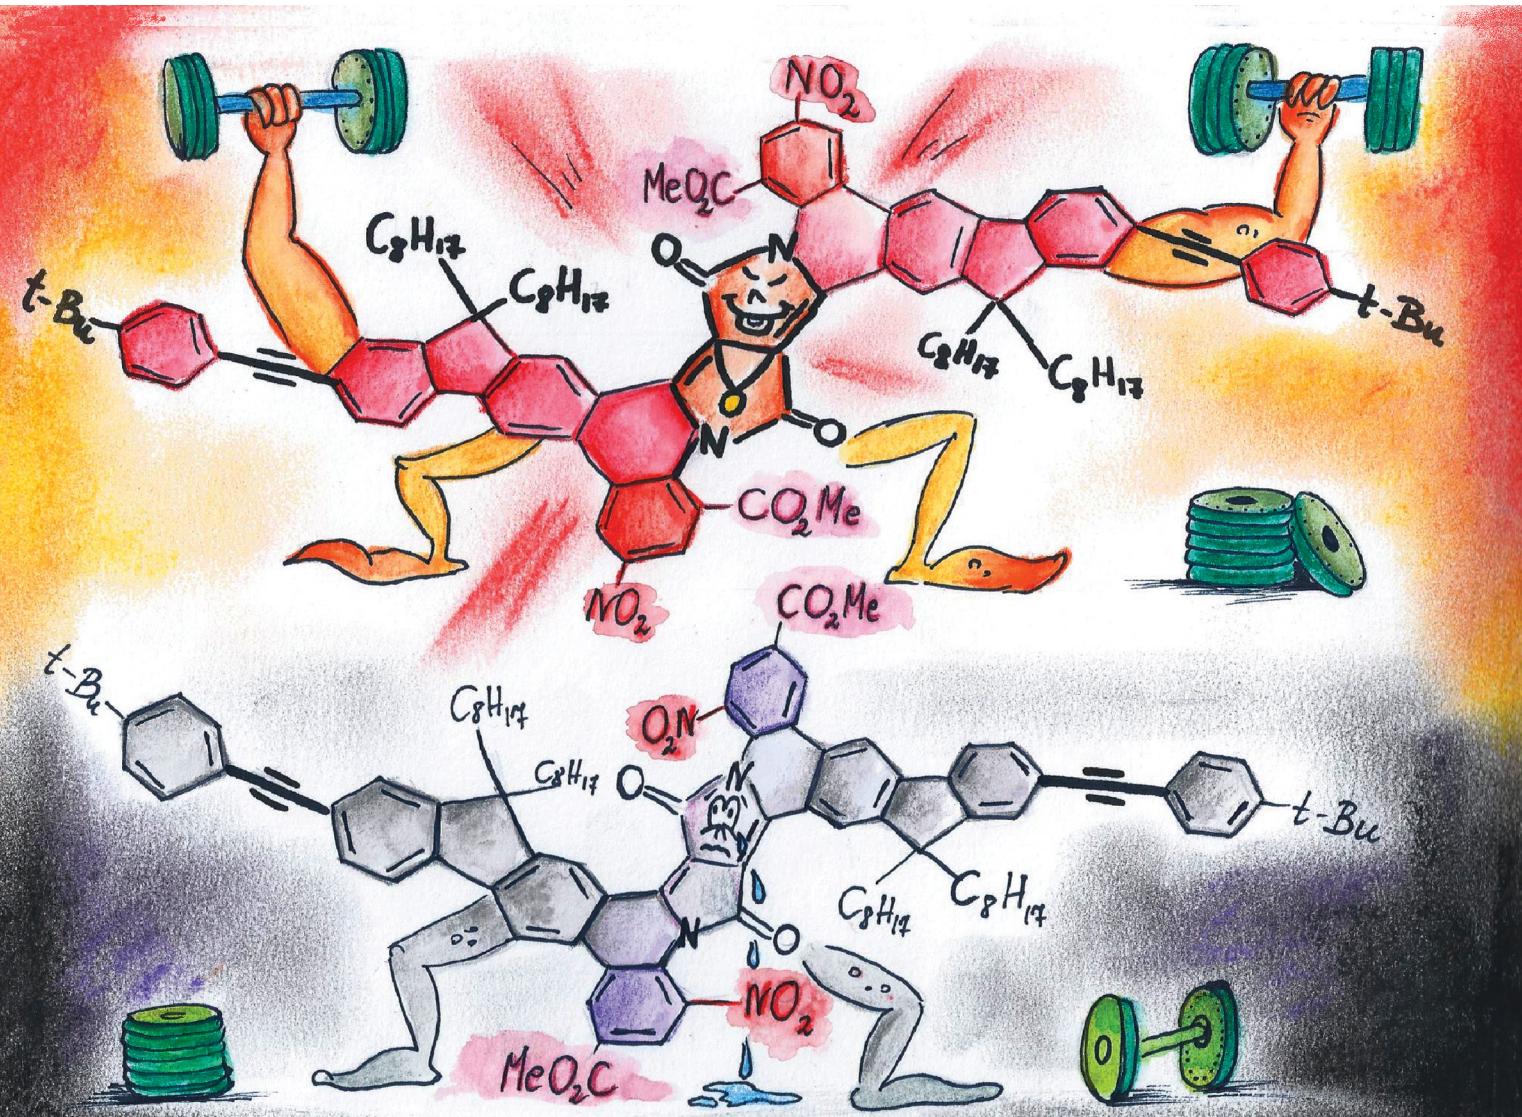

ISSN 1463-9076



Cite this: *Phys. Chem. Chem. Phys.*, 2025, 27, 5965

## How the nitro group position determines the emission properties of $\pi$ -expanded diketopyrrolopyrroles<sup>†</sup>

Kamil Skonieczny, <sup>‡a</sup> Francesco Di Maiolo, <sup>‡c</sup> Sara Venturi, <sup>‡b</sup> Alessandro Iagatti, <sup>bd</sup> Alessandro Ricci, <sup>c</sup> Francesco Bertocchi, <sup>c</sup> Daniel T. Gryko <sup>\*a</sup> and Andrea Lapini <sup>\*bcd</sup>

Two complex  $\pi$ -expanded diketopyrrolopyrroles (EDPPs) have been prepared following a multistep but straightforward strategy. We discovered that the fate of these molecules in the excited state can be controlled by subtle differences in their structure. When  $\text{NO}_2$  groups are located at a distant position, the quadrupolar, centrosymmetric dye exhibits strong red emission across the solvents' polarity scale. However, when  $\text{NO}_2$  groups are adjacent to the lactam moiety, the EDPPs exhibit negligible emission even in non-polar solvents. Density functional theory (DFT) calculations indicate that the primary distinction between the two molecules lies in the structural planarity. The molecule with  $\text{NO}_2$  groups adjacent to the lactam moiety exhibits a loss of planarity due to the coulombic repulsion between these groups. The calculations also suggest that the nitro group does not participate in the  $S_0 \rightarrow S_1$  excitation. Furthermore, for both compounds, the first two excited states (one bright and one dark) are found to be very close in energy. The change in molecular geometry affects the non-radiative deactivation of excited states, leading to the two distinct emission behaviors. Experiments in a glassy solvent at low temperatures reveal that at 77 K the photophysics of both dyes becomes the same, which proves that thermal activation is the key mechanism for the non-radiative decay of the excited state for non-emissive EDPPs.

Received 12th December 2024,  
Accepted 16th December 2024

DOI: 10.1039/d4cp04689g

rsc.li/pccp

### Introduction

The design of organic analogs of *n*-doped semiconductors benefits from electron-deficient aromatic  $\pi$ -conjugated molecules.<sup>1</sup> They can also serve as light sensitizers for photooxidation and for initiating charge transfer (CT) *via* hole transduction.<sup>2</sup> The most typical approach for decreasing the electron density is to attach electron-withdrawing substituents, and the nitro group is one of the strongest of them (Hammett constants exceeding 0.7).<sup>3</sup> Nitro-aromatics have been widely utilized in various applications involving intramolecular charge transfer (CT),<sup>4</sup> fluorescent

probes,<sup>5</sup> and nonlinear optical materials.<sup>6</sup> With a few exceptions, however, nitro-aromatics were historically regarded as non-emissive.<sup>7</sup> The scattered examples of fluorescent nitroaromatics were regarded as a curiosity and hardly influenced the mainstream of functional dyes' chemistry. The discovery of strongly emissive nitro-aromatics in the last decade enabled a partial change of this paradigm.<sup>8</sup> Several quadrupolar, centrosymmetric nitro-aromatics were discovered and investigated.<sup>9</sup> This in turn led to attempts to formulate some general rules governing their strong emission.<sup>10</sup>

$\pi$ -Expanded diketopyrrolopyrroles<sup>11</sup> were thought to present an ideal synthetic platform for modular access to centrosymmetric nitroaromatics. We recently reported the synthesis of a new class of  $\pi$ -expanded diketopyrrolopyrroles (EDPPs), which exhibit strong fluorescence in various solvents despite the presence of  $\text{NO}_2$  groups in their structure.<sup>9a</sup> The target molecules were synthesized in a two-step process which involved the *N*-arylation of DPPs followed by an intramolecular direct arylation of the aromatic rings that are present in these building blocks. This established synthetic pathway prompted us to synthesize other pigments, especially those in which the  $\text{NO}_2$  group is in a different position. Earlier observations indicated that the position of the nitro group in relation to the  $\pi$ -system core has a

<sup>a</sup> Institute of Organic Chemistry of Polish Academy of Sciences, Kasprzaka 44/52, 01-224 Warsaw, Poland. E-mail: dtgryko@icho.edu.pl

<sup>b</sup> LENS (European Laboratory for Non-Linear Spectroscopy), Via N. Carrara 1, 50019 Sesto Fiorentino, Italy. E-mail: andrea.lapini@unipr.it

<sup>c</sup> Department of Chemistry, Life Sciences and Environmental Sustainability, University of Parma, Parco Area delle Scienze 17/A, 43124 Parma, Italy

<sup>d</sup> Istituto Nazionale di ottica CNR-INO, Via Nello Carrara 1 50019 Sesto Fiorentino, Italy

<sup>†</sup> Electronic supplementary information (ESI) available: Details of the synthesis, spectroscopic characterisation, and crystallographic and computational data. See DOI: <https://doi.org/10.1039/d4cp04689g>

<sup>‡</sup> These authors contributed equally.



profound influence on fluorescence.<sup>9b</sup> Here we report how competing excited state processes decide about the fate of centrosymmetric nitro-aromatics in the excited state, by determining their emissivity. To achieve this, we first designed a suitable DPP core containing alkylated fluorene, which ensured photophysical properties in the near-infrared region and provided appropriate solubility of the final dyes.


## Results and discussion

### Synthesis

At the outset we focused on the preparation of DPP **1** containing bromine atoms on the fluorene unit, which was achieved following

the previously reported literature procedure (Scheme 1).<sup>11j</sup> The pigment was then modified by introducing an arylalkyne substituent. In order to enable the solubilization of the starting material in solvents commonly used in organic synthesis, the nitrogen atoms of the lactam core were protected with *tert*-butoxycarbonyl groups (Boc). The formed bis-Boc-DPP **2** was then subjected to Sonogashira coupling with 4-*tert*-butylphenylacetylene which resulted in the formation of DPP **3**.

It is important to note that the reaction must be carried out at a temperature equal to or below 80 °C, otherwise it leads to a mixture of products due to partial deprotection of the Boc groups of the substrate. Finally, the product of the double Sonogashira reaction *i.e.* DPP **3** was deprotected by adding

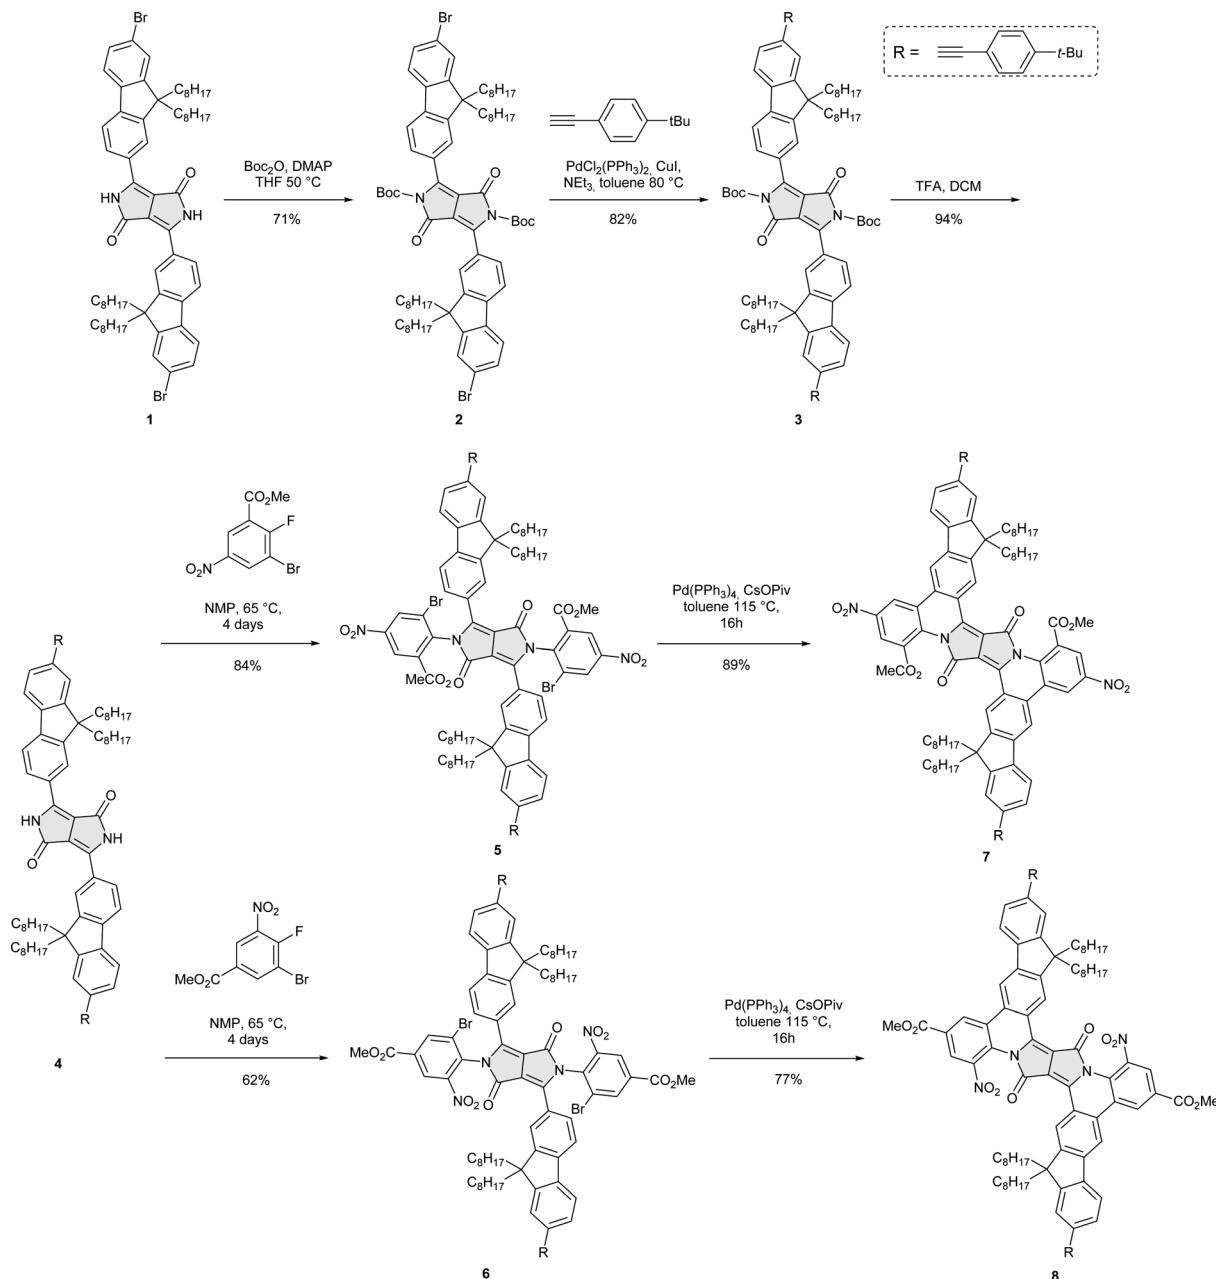

Scheme 1 The preparation of DPPs **7** and **8**.



TFA to the pigment solution in methylene chloride. This generated free DPP **4** in the quantitative reaction yield (Scheme 1). Subsequently, *N*-arylation of DPP **4** was carried out with electron-poor aryl fluorides namely methyl 3-bromo-2-fluoro-5-nitrobenzoate and methyl 3-bromo-4-fluoro-5-nitrobenzoate, in the presence of potassium carbonate in NMP (Scheme 1). The reaction was completed after 4 days, yielding **5** and **6**, respectively. *N*-arylation of DPP **4** proceeded much slower compared to the previously described DPP bearing benzofuran units, where the reaction was completed after a few hours.<sup>9a</sup> In the next step, both **5** and **6** were subjected to  $\text{Pd}(\text{PPh}_3)_4$  in order to perform intramolecular, direct arylation in our systems. As a result we obtained good yields of two  $\pi$ -expandable products: **7** and **8**, both possessing 12 fused rings. The reaction was carried out overnight in dry toluene at 115 °C. Both target pigments are soluble in chlorinated and aromatic solvents, which enabled their identification using  $^1\text{H}$  NMR and  $^{13}\text{C}$  NMR spectroscopies.

### Steady-state optical absorption and emission

Absorption, emission and excitation spectra of dyes **7** and **8** have been recorded in various solvents with different polarity properties (Table 1 and Fig. 1). These spectra are characterized by an absorption band in the 500–650 nm spectral range as well as through a pronounced vibronic progression ( $\approx 1520 \text{ cm}^{-1}$ ); however, only a slight modification in the spectral bandwidth and the position of the absorption maximum has been observed as a function of solvent polarity. Excitation and fluorescence spectra are very poorly solvent-dependent as well.

Fluorescence quantum yields ( $\Phi_{\text{fl}}$ ) reveal dramatically opposite behavior between dyes **7** ( $\Phi_{\text{fl}} = 0.76$ ) and **8** ( $\Phi_{\text{fl}} = 0.09$ ) in non-polar and slightly polar solvents ( $\text{CCl}_4$  and toluene). At the same time a decreasing trend in the fluorescence quantum yield is observed for both compounds as the polarity of the environment is increased ( $\Phi_{\text{fl}} = 0.16$  for dyes **7** and  $\Phi_{\text{fl}} = 0.03$  for **8** in BZN). The virtually absent response of the emission maximum ( $\lambda_{\text{em}}^{\text{max}}$ ) to solvent polarity for both dyes **7** and **8** indicates that the emissive excited state may be described as quadrupolar. However, the fluorescence emission quenching (for dyes **7** and **8**) as the polarity of the solvent is increased from dye **7** to **8** suggests that an additional excited state plays a key role in the deactivation pathway. Given that molar absorption coefficients are  $\approx 140\,000 \text{ M}^{-1} \times \text{cm}^{-1}$  in both cases, the optical brightness for **7** reaches almost  $110\,000 \text{ M}^{-1} \times \text{cm}^{-1}$  in toluene. This value should be compared from one site with optical brightness  $\approx 170\,000 \text{ M}^{-1} \times \text{cm}^{-1}$  recorded for somehow

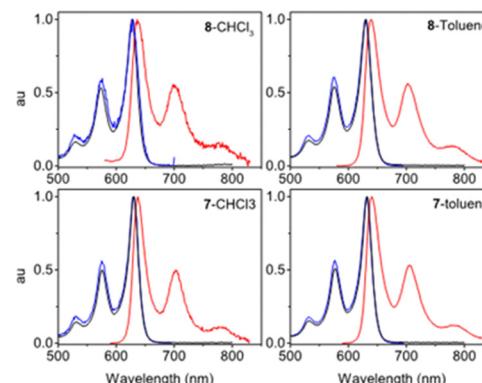


Fig. 1 Absorption, emission and excitation spectra of dyes **7** and **8** in  $\text{CHCl}_3$  (left panels) and toluene (right panels). Spectra recorded in  $\text{CCl}_4$ , THF,  $\text{CH}_2\text{Cl}_2$  and benzonitrile are included in the ESI.†

analogous  $\pi$ -expanded diketopyrrolopyrrole bearing fused fluorene units and flanking diarylamino groups.<sup>11j</sup> The presence of nitro groups does not increase the fluorescence quantum yield. On the other hand it slightly decreases the molar absorption coefficient. The optical brightness of EDPP **7** compared however with other described nitro-aromatics is one of the largest recorded.<sup>10</sup>

### Time resolved measurements

To disentangle the mechanism leading to the fluorescence emission properties of dyes **7** and **8**, we characterized the relaxation dynamics with pump-probe spectroscopy in the UV-vis, NIR and Mid-IR spectral range.

UV-vis pump-probe spectra in the 400–750 nm spectral range have been recorded with an excitation wavelength range of 525–530 nm for various solvents using the transient absorption setup described in the ESI.† All spectra show ground state bleaching plus stimulated emission signals and an excited state absorption located at 470 nm. Spectra as a function of time have been analyzed with a global fitting approach using the Glotaran program package<sup>9</sup> and the unidirectional sequential model as the kinetic decaying scheme. The analysis showed that both dyes **7** and **8** contain only one main spectral component that relaxes back to the ground state (some representative transient absorption spectra are reported in Fig. S7 and S8 in the ESI†); the additional stimulated emission increases and slight red-shift (for the  $\approx 700 \text{ nm}$  band) observed in the first tens of picoseconds (Fig. S8a and b, ESI†) have been ascribed to vibrational and structural relaxation following the new charge

Table 1 Excited state lifetimes ( $t$ ) and constants ( $k$ ), fluorescence quantum yields ( $\Phi_{\text{fl}}$ ), radiative ( $k_r$ ) and non-radiative ( $k_{\text{nr}}$ ) decay constants. Tol = toluene, THF = tetrahydrofuran, BZN = benzonitrile

<b>7</b>					<b>8</b>					
$t$ (ns)	$(k_r + k_{\text{nr}})$ ( $\text{ns}^{-1}$ )	$\Phi_{\text{fl}}$	$k_r$ ( $\text{ns}^{-1}$ )	$k_{\text{nr}}$ ( $\text{ns}^{-1}$ )	$t$ (ns)	$(k_r + k_{\text{nr}})$ ( $\text{ns}^{-1}$ )	$\Phi_{\text{fl}}$	$k_r$ ( $\text{ns}^{-1}$ )	$k_{\text{nr}}$ ( $\text{ns}^{-1}$ )	
$\text{CCl}_4$	3.400	0.29	0.76	0.22	0.07	0.679	1.47	0.09	0.13	1.34
Tol	3.548	0.28	0.77	0.22	0.06	0.484	2.07	0.09	0.19	1.88
$\text{CHCl}_3$	0.340	1.59	0.09	0.26	2.60	0.032	31.25	0.004	0.13	31.1
THF	2.579	0.39	0.56	0.22	0.17	0.141	7.09	0.02	0.14	6.9
$\text{CH}_2\text{Cl}_2$	0.158	6.33	0.04	0.25	6.08	0.022	45.5	0.003	0.14	45.3
BZN	0.863	1.16	0.16	0.19	0.97	0.067	14.9	0.03	0.45	14.5



distribution in the excited state. The time constants for ground state recovery are strongly solvent dependent, as suggested by fluorescence quantum yields, and are reported in Table 1.

Fluorescence lifetimes were determined by time correlated single photon counting and supported by comparison to the decay kinetics of the bleaching signal acquired with pump-probe. The agreement of the two techniques allowed the exploitation of the latter to determine the fast ground state relaxation observed for EDPP **8**. Ground state recovery dynamics allowed us to highlight that radiative decay constants are, as expected, solvent independent and very much similar for dyes **7** and **8** (see Table 1); in contrast, non-radiative processes are strongly influenced by solvent environment and by the position of nitro-groups. In more detail, the non-radiative constant increases by increasing the solvent polarity and even higher non-radiative constant (one order of magnitude larger on average) are observed when moving from compound **7** to compound **8**, suggesting that in both cases a second non-radiative decay channel is opened. UV-vis pump-probe data are fully in agreement with the presence of an additional excited state with a more pronounced charge transfer (CT) character in the relaxation pathway. The fluorescence quantum yields measured in  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$  do not follow the solvent polarity trend response observed for other solvents.

Pump-probe measurements evidence that ground state recovery take place at a few hundred picoseconds for dye **7** and tens of picoseconds for dye **8**.<sup>12</sup> This evidence suggests that both solvents may come into specific molecular interactions with dyes **7** and **8** as a result of their low but not negligible capability, to enhance the non-radiative decay<sup>13</sup> and form hydrogen-bonding with molecules in the excited electronic state. It is worth mentioning that among the various solvents used to characterize the properties of excited state compounds **7** and **8**, chloroform and dichloromethane are the only ones having hydrogen bonding donor properties and are the ones where both compounds have the shortest lifetimes (no evidence of triplet state formation from pump-probe data). Due to the extended delocalization of the electron density for both dyes **7** and **8**, we expected, in analogy with formerly reported quadrupolar molecules,<sup>9a</sup> NIR excited state absorptions to take place. Pump-probe measurements in the 800–910 nm spectral range have been performed for both compounds in toluene and chloroform solutions using the US-pp setup<sup>15</sup> described in the ESI† and the global analysis results have been reported as shown in Fig. 2. In chloroform, both dyes **7** and **8** showed a broader spectral shape than in toluene as well as a slight time-dependent blue shift of the band maximum; which is practically absent in toluene. Dynamical spectral shift and spectral broadening are very common markers for the stabilization of excited states. This is due to polar and slightly polar solvents, strongly suggesting that excited state absorption involves a state characterized by a certain degree of charge separation.

Global analysis, within a two-component sequential model scheme, revealed that one main spectral component relaxes back to the ground state, with the time constant of this process being in very good agreement with that of the ground state

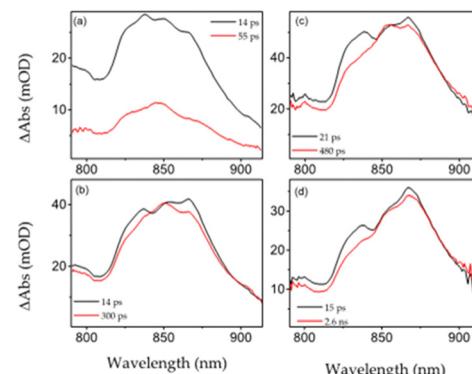


Fig. 2 Evolution associated decay spectra (EADS) of transient absorption measurements in the NIR spectral region for: **8** in  $\text{CHCl}_3$  (a), **7** in  $\text{CHCl}_3$  (b), **8** in toluene (c) and **7** in toluene (d).

bleaching decay. The first picosecond component has been ascribed to intramolecular structural relaxation. Transient infrared spectra (Fig. S13, ESI†) are in good agreement with the UV-vis pump-probe, showing ground state recovery on the hundred's picosecond timescale for EDPP **8** in THF.<sup>14</sup> Additional evidence that the presence of a CT state plays the key role in determining fluorescence properties of dyes **7** and **8** has been obtained from temperature-dependent fluorescence lifetime measurements in 2Me-THF. The data are reported as shown in Fig. 3 and Fig. S10 (ESI†). Dye **7** shows no temperature dependence from 298 K to 77 K, while EDPP **8** evidences a clear increase in fluorescence lifetimes upon cooling down the solution. Broadband pump-probe measurements in the visible spectral range have been also performed in a frozen solvent and at room temperature. Results, reported in Fig. 3 and Fig. S11 and S12 of the ESI,† show no spectral shift in the first 200 ps, in net contrast to room temperature, demonstrating that in a glassy solvent, the structural relaxation is blocked.

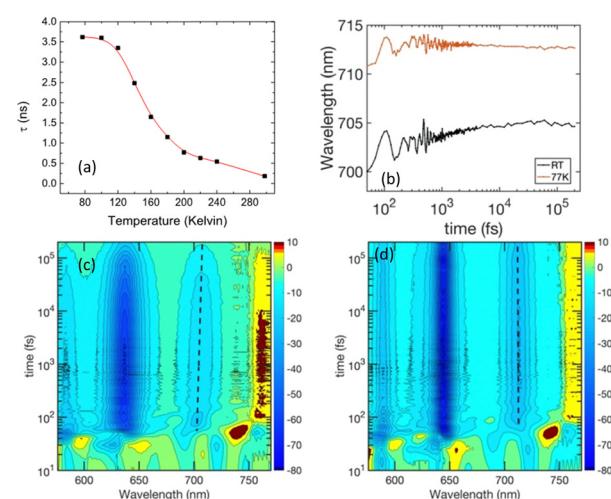


Fig. 3 Temperature dependence of the fluorescence lifetime for dye **8** in 2Me-THF solution (a). Wavelength of the minimum of the stimulated emission signal (b) from broadband pump-probe maps at room temperature (c) and 77 K (d).



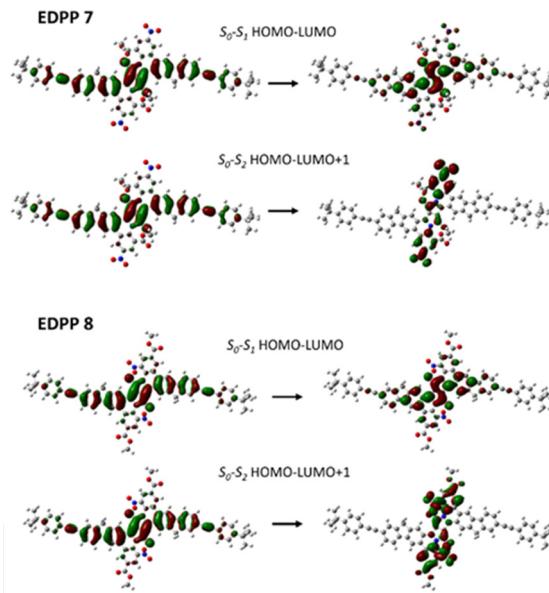


Fig. 4 The two lowest lying singlet excited states at the Franck–Condon geometry in dyes **7** and **8**. The most important Kohn–Sham molecular orbitals involved in the transitions are shown. Calculations performed at the TD-DFT level (B3LYP/6-31+G(d,p)).

These results suggest that both thermal activation and structural relaxation play key roles in the radiative and non-radiative decay mechanisms of excited states EDPPs **7** and **8**.

### First principle calculations and modeling

We have performed quantum chemistry calculations for both dyes **7** and **8**. Ground state ( $S_0$ ) optimized geometries have been obtained at the DFT level (B3LYP/6-31+G(d,p)), whereas the first few excited states have been calculated relying on the time-dependent DFT (TD-DFT) approach (B3LYP/6-31+G(d,p)). All the calculations have been performed in the gas phase using the Gaussian16 (Revision B.01) package.<sup>16</sup> A fairly notable difference between the two molecules occurs already at the level of the ground state geometry, with dye **7** being planar and EDPP **8** showing a bent geometry ( $\approx 160^\circ$ , see Fig. S4 in the ESI†). TD-DFT calculations show that in dyes **7** and **8** the bright, lowest, excited state  $S_1$  corresponds to a  $\pi-\pi^*$  (HOMO  $\rightarrow$  LUMO) transition, which involves two fluorenes and the DPP core, with almost no contribution coming from the nitro-groups (see Fig. 4). The relevant oscillator strengths are high, ranging from 1.54 for dye **8** to 1.6 for EDPP **7**. Steady-state absorption and emission spectra in Fig. 1 correspond to transitions that mainly involve  $S_1$ . On the other hand, in both dyes **7** and **8**, the second singlet excited state  $S_2$  corresponds to a HOMO  $\rightarrow$  LUMO+1 transition with a large involvement of the nitro-groups and a strong quadrupolar charge-transfer (CT) character (see Fig. 3). As a result,  $S_2$  is optically dark and has no influence in the steady state spectra (see Fig. 1). At the same time, being very close in energy to  $S_1$  in the Franck–Condon region,  $S_2$  is involved in the solvent-dependent non-radiative processes discussed in the previous section (Fig. 5).

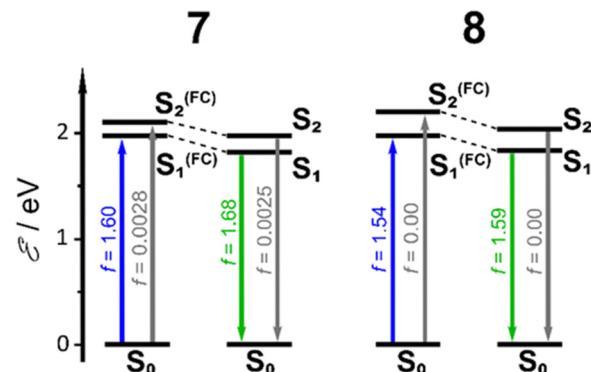


Fig. 5 Excited state energy levels obtained from TD-DFT calculations in the gas phase for compounds EDPP **7** and EDPP **8**; oscillators' strength is reported in brackets.

Our recent analysis of the literature<sup>10</sup> on fluorescent nitroaromatics has shown that there are two major scenarios of the dependence of fluorescence intensity on solvent polarity, which originates from the interplay between ISC and CT once the molecules reach their  $S_1$  states. Indeed in most cases, the fluorescent nitroaromatics' emission strength decreases as the medium polarity increases. In the case of nitro-stilbenes however, fluorescence intensity is low in non-polar solvents and it increases in media of intermediate polarity or strong polarity.<sup>4,7i,j</sup> This is related to suppressing intersystem crossing in moderately polar solvents. Interestingly in the case of nitro-1,4-distyrylbenzenes Spalletti and co-workers claim that the structure of emissive  $^1\text{ICT}^*$  state does not lose planarity even in very polar solvents and the fluorescence is not quenched in e.g. DMF.<sup>7i,j</sup> In other words excited state dynamics in polar media facilitates the population of a planar  $^1\text{ICT}^*$  state resulting in strong emission. The emphasis on the importance of planarity bears a strong resemblance to our findings.

### Conclusions

By implementing very subtle changes in the structures of two regioisomeric, quadrupolar, centrosymmetric,  $\pi$ -expanded diketopyrrolopyrroles, it is possible to completely alter their emissive properties. Moving nitro groups from a distant position to the  $\text{sp}^2$  carbon atom close to the  $\text{C}=\text{O}$  bond decreases the fluorescence intensity by a factor of 10. In contrast, placing the nitro group at a distant position leads to a super strong emitter with optical brightness  $\approx 110\,000\text{ M}^{-1} \times \text{cm}^{-1}$  at 635 nm. TD-DFT computations for dyes **7** and **8**, indicate, that upon excitation, these molecules reach a bright  $S_1$  state characterized by  $\pi\pi^*$  nature, with the energy of the dark  $S_2$  state being only slightly higher than that of  $S_1$  (Fig. 5). Unlike dye **7**, EDPP **8**, once in the bright  $S_1$  state, undergoes a rapid internal conversion to the dark  $S_2$  state through thermal activation.<sup>17</sup> Photophysical studies in frozen glass provide convincing evidence that the rate constant  $k_{\text{nr}}$  for the non-emissive EDPP reaches values comparable to those of the emissive DPP below 120 K. Broadband pump–probe suggests that the thermally

activated internal conversion through the CT  $S_2$  state is mediated by intramolecular structural relaxation. The fundamental difference between dyes **7** and **8** arises from the fact that the presence of the nitro group at the *ortho* position relative to the bridge with the DPP core, is sufficient to induce non-planarity in both the ground state and excited state conformations of dye **8**. In this context, the presence of the nitro group plays a decisive role, as the coulombic repulsion between the negative charges (with the second being the oxygen of the C=O group) results in a non-planar conformation. In the broader context, a comparison of these findings with some earlier results<sup>9b</sup> points out the following: in the case of larger polarized dyes, the molecules which possess nitro groups in positions that enable a maintaining the planarity of the  $\pi$ -system tend to show strong fluorescence. Their excellent properties such as large optical brightness open the door for future applications in optoelectronics. Given the recent renaissance of interest in nitroaromatics this work should inspire the future design of strongly emitting fluorophores bearing  $\text{NO}_2$  groups, with distinctive  $\pi$ -expanded architectures.

## Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

## Data availability

All experimental details and data supporting this article are available in the ESL.<sup>†</sup>

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The work was financially supported by the Polish National Science Center, Poland (OPUS 2020/37/B/ST4/00017) and the Foundation for Polish Science (TEAM POIR.04.04.00-00-3CF4/16-00). The support from the Italian Ministry of Research through the project 20225NPY8P (LANTERN), through the project P2022ALSMP\_002 (VISIO) and the IPHOQS project is acknowledged. The support from Parma University through the project SFM-CARS is also gratefully acknowledged. F. D. M. acknowledges financial support from Bando di ateneo per la ricerca 2023 – azione B. This work benefited from the support of the HPC (High Performance Computing) facility at the University of Parma. F. D. M. acknowledges the CINECA award under the ISCRA initiative, for the availability of high-performance computing resources and support (project IsCb8 InveST (HP10CIDH42)). F. D. M. position was co-funded by the European Union – PON Research and Innovation 2014-2020. AL would like to acknowledge Alessio Montori from LENS Electronic Workshop for his

contribution to the development of the experimental signal acquisition. We thank N. D. G. for amending the manuscript.

## Notes and references

- 1 A. Nowak-Król, K. Shoyama, M. Stolte and F. Würthner, Naphthalene and perylene diimides – better alternatives to fullerenes for organic electronics?, *Chem. Commun.*, 2018, **54**, 13763–13772.
- 2 S.-H. Wen, A. Li, J. Song, W.-Q. Deng, K.-L. Han and W. A. Goddard, III, First-principles investigation of anisotropic hole mobilities in organic semiconductors, *J. Phys. Chem. B*, 2009, **113**, 8813–8819.
- 3 C. Hansch, A. Leo and R. W. Taft, A survey of Hammett substituent constants and resonance and field parameters, *Chem. Rev.*, 1991, **91**, 165–195.
- 4 (a) H. Görner and D. Schulte-Frohlinde, Study of the trans → cis photoisomerization of 4-nitro-4'-dimethylaminostilbene in toluene solutions, *J. Mol. Struct.*, 1982, **84**, 227–236; (b) H. Görner, Photophysics and photochemistry of trans-4-nitrostilbenes and trans-2,4-dinitrostilbenes: Effect of intramolecular charge transfer, *Ber. Bunsenges. Phys. Chem.*, 1998, **102**, 726–737.
- 5 T. Ueno, Y. Urano, H. Kojima and T. Nagano, Mechanism-Based Molecular Design of Highly Selective Fluorescence Probes for Nitritative Stress, *J. Am. Chem. Soc.*, 2006, **128**, 10640–10641.
- 6 C.-K. Wang, P. Macak, Y. Luo and H. Ågren, Effects of  $\pi$  centers and symmetry on two-photon absorption cross sections of organic chromophores, *J. Chem. Phys.*, 2001, **114**, 9813–9820.
- 7 (a) M.-C. Chen, D.-G. Chen and P.-T. Chou, Fluorescent Chromophores Containing the Nitro Group: Relatively Unexplored Emissive Properties, *ChemPlusChem*, 2021, **86**, 11–27; (b) D. J. Cowley, Triplet-Triplet Absorption Spectroscopy of Some Highly Dipolar Unsaturated Nitro Compounds, *Helv. Chim. Acta*, 1978, **61**, 184–197; (c) B. Bursa, D. Wróbel, B. Barszcz, M. Kotkowiak, O. Vakuliuk, D. T. Gryko, Ł. Kolanowski, M. Baraniak and G. Lota, The impact of solvents on the singlet and triplet states of selected fluorine corroles – absorption, fluorescence, and optoacoustic studies, *Phys. Chem. Chem. Phys.*, 2016, **18**, 7216–7228; (d) E. F. Plaza-Medina, W. Rodríguez-Córdoba and J. Peón, Role of Upper Triplet States on the Photophysics of Nitrated Polyaromatic Compounds: S-1 Lifetimes of Singly Nitrated Pyrenes, *J. Phys. Chem. A*, 2011, **115**, 9782–9789; (e) J.-M. Mewes, V. Jovanović, C. M. Marian and A. Dreuw, On the molecular mechanism of non-radiative decay of nitrobenzene and the unforeseen challenges this simple molecule holds for electronic structure theory, *Phys. Chem. Chem. Phys.*, 2014, **16**, 12393–12406; (f) C. E. Crespo-Hernández, G. Burdzinski and R. Arce, Environmental Photochemistry of Nitro-PAHs: Direct Observation of Ultrafast Intersystem Crossing in 1-Nitropyrene, *J. Phys. Chem. A*, 2008, **112**, 6313–6319; (g) E. M. Espinoza,



B. Xia, N. Darabedian, J. M. Larsen, V. Nuñez, D. Bao, J. T. Mac, F. Botero, M. Wurch, F. Zhou and V. I. Vullev, Nitropyrene Photoprobe: Making Them, and What Are They Good for?, *Eur. J. Org. Chem.*, 2016, 343–356; (h) K. Rybicka-Jasińska, E. M. Espinoza, J. A. Clark, J. B. Derr, G. Carlos, M. Morales, M. K. Billones, O. O'Mari, H. Ågren, G. V. Baryshnikov and V. I. Vullev, Making Nitronaphthalene Fluoresce, *J. Phys. Chem. Lett.*, 2021, **12**, 10295–10303; (i) B. Carlotti, F. Elisei, U. Mazzucato and A. Spaletti, Unusual high fluorescence of two nitro-distyrylbenzene-like compounds induced by CT processes affecting the fluorescence/intersystem-crossing competition, *Phys. Chem. Chem. Phys.*, 2015, **17**, 14740–14749; (j) S. Ciorba, G. Galiazzo, U. Mazzucato and A. Spaletti, Photobehavior of the Geometrical Isomers of Two 1,4-Distyrylbenzene Analogues with Side Groups of Different Electron Donor/Acceptor Character, *J. Phys. Chem. A*, 2010, **114**, 10761–10768; (k) P.-Y. Wang, Y.-C. Hsu, P. H. Chen, G.-Y. Chen, Y.-K. Liao and P.-Y. Cheng, Solvent-polarity dependence of ultrafast excited-state dynamics of trans-4-nitrostilbene, *Phys. Chem. Chem. Phys.*, 2024, **26**, 788–807; (l) B. Sadowski, M. Kaliszewska, G. Clermont, Y. M. Poronik, M. Blanchard-Desce, P. Piątkowski and D. T. Gryko, Realization of nitroaromatic chromophores with intense two-photon brightness, *Chem. Commun.*, 2023, **59**, 11708–11711; (m) Q. He, F. Dong, L. Xing, H. He, X. Chen, H. Wang, S. Ji and Y. Huo, The effects of 1-and 3-positions substitutions on the photo-physical properties of perylene and its application in thiol fluorescent probes, *Tetrahedron*, 2022, **104**, 132565.

8 (a) P. B. Ghosh and M. W. Whitehouse, 7-chloro-4-nitrobenzo-2-oxa-1,3-diazole: a new fluorogenic reagent for amino acids and other amines, *Biochem. J.*, 1968, **108**, 155–156; (b) S. Benson, A. Fernandez, N. D. Barth, F. De Moliner, M. H. Horrocks, C. S. Herrington, J. L. Abad, A. Delgado, L. Kelly, Z. Chang, Y. Feng, M. Nishiura, Y. Hori, K. Kikuchi and M. Vendrell, SCOTfluors: Small, Conjugatable, Orthogonal, and Tunable Fluorophores for In Vivo Imaging of Cell Metabolism, *Angew. Chem., Int. Ed.*, 2019, **58**, 6911–6915; (c) M.-C. Chen, Y.-L. Lee, Z.-X. Huang, D.-G. Chen and P.-T. Chou, Tuning Electron Withdrawing Strength on Phenothiazine Derivatives: Achieving 100% Photoluminescence Quantum Yield by NO<sub>2</sub> Substitution, *Chem. – Eur. J.*, 2020, **26**, 7124–7130.

9 (a) K. Skonieczny, I. Papadopoulos, D. Thiel, K. Gutkowski, P. Haines, P. M. McCosker, A. D. Laurent, P. A. Keller, T. Clark, D. Jacquemin, D. M. Guldi and D. T. Gryko, How To Make Nitroaromatic Compounds Glow: Next-Generation Large X-Shaped, Centrosymmetric Diketopyrrolopyrroles, *Angew. Chem., Int. Ed.*, 2020, **59**, 16104–16113; (b) Y. M. Poronik, G. V. Baryshnikov, I. Deperasińska, E. M. Espinoza, J. A. Clark, H. Ågren, D. T. Gryko and V. I. Vullev, Deciphering the unusual fluorescence in weakly coupled bis-nitro-pyrrolo[3,2-b]pyrroles, *Commun. Chem.*, 2020, **3**, 190; (c) B. Sadowski, M. Kaliszewska, Y. P. Poronik, M. Czichy, P. Janasik, M. Banasiewicz, D. Mierzwa, W. Gadomski, T. D. Lohrey, J. A. Clark, M. Łapkowski, B. Kozankiewicz, V. I. Vullev, A. L. Sobolewski, P. Piątkowski and D. T. Gryko, Strategy Towards Strongly Emissive Nitroaromatics Through a Weakly Electron-Deficient Core, *Chem. Sci.*, 2021, **12**, 14039–14049.

10 Y. M. Poronik, B. Sadowski, K. Szychta, F. H. Quina, V. I. Vullev and D. T. Gryko, Revisiting the non-fluorescence of nitroaromatics: presumption versus reality, *J. Mater. Chem. C*, 2022, **10**, 2870–2904.

11 (a) G. M. Fischer, A. P. Ehlers, A. Zumbusch and E. Daltrozzo, Near-Infrared Dyes and Fluorophores Based on Diketopyrrolopyrroles, *Angew. Chem., Int. Ed.*, 2007, **46**, 3750–3753; (b) S. Shimizu, T. Iino, Y. Araki and N. Kobayashi, Pyrrolopyrrole aza-BODIPY analogues: A facile synthesis and intense fluorescence, *Chem. Commun.*, 2013, **49**, 1621–1623; (c) S. Shimizu, T. Iino, A. Saeki, S. Seki and N. Kobayashi, Rational Molecular Design towards Vis/NIR Absorption and Fluorescence by using Pyrrolopyrrole aza-BODIPY and its Highly Conjugated Structures for Organic Photovoltaics, *Chem. – Eur. J.*, 2015, **21**, 2893–2904; (d) S. Shimizu, Aza-BODIPY synthesis towards vis/NIR functional chromophores based on a Schiff base forming reaction protocol using lactams and heteroaromatic amines, *Chem. Commun.*, 2019, **55**, 8722–8743; (e) Y. Kage, S. Mori, M. Ide, A. Saeki, H. Furuta and S. Shimizu, Blackening of aza-BODIPY analogues by simple dimerization: panchromatic absorption of a pyrrolopyrrole aza-BODIPY dimer, *Mater. Chem. Front.*, 2018, **2**, 112–120; (f) W. Yue, S.-L. Suraru, D. Bialas, M. Müller and F. Würthner, Synthesis and Properties of a New Class of Fully Conjugated Azahexacene Analogues, *Angew. Chem., Int. Ed.*, 2014, **53**, 6159–6162; (g) M. Grzybowski, E. Glodkowska-Mrowka, T. Stoklosa and D. T. Gryko, Bright, Color-Tunable Fluorescent Dyes Based on  $\pi$ -Expanded Diketopyrrolopyrroles, *Org. Lett.*, 2012, **14**, 2670–2673; (h) M. Grzybowski and D. T. Gryko, *US Pat.*, US20140357869A1, 2015; (i) D. T. Gryko, M. Grzybowski, P. Hayoz and A. Jeżewski, *US Pat.*, US9698348B2, 2017; (j) M. Grzybowski, V. Hugues, M. Blanchard-Desce and D. T. Gryko, Two-Photon-Induced Fluorescence in New  $\pi$ -Expanded Diketopyrrolopyrroles, *Chem. – Eur. J.*, 2014, **20**, 12493–12501; (k) F. Trilling, O. Sachnik and U. Scherf,  $\pi$ -Expanded diketopyrrolopyrroles as acceptor building blocks for the formation of novel donor–acceptor copolymers, *Polym. Chem.*, 2019, **10**, 627–632; (l) L. Ma, B. Chen, Y. Guo, Y. Liang, D. Zeng, X. Zhan, Y. Liu and X. Chen, NIR polymers and phototransistors, *J. Mater. Chem. C*, 2018, **6**, 13049–13058; (m) B. Chen, Y. Yang, P. Cheng, X. Chen, X. Zhan and J. Qin, designing a thiophene-fused DPP unit to build an A–D–A molecule for solution-processed solar cells, *J. Mater. Chem. A*, 2015, **3**, 6894–6900; (n) E. Gońka, L. Yang, R. Steinbock, F. Pesciaioli, R. Kuniyil and L. Ackermann,  $\pi$ -Extended Polyaromatic Hydrocarbons by Sustainable Alkyne Annulations through Double C–H/N–H Activation, *Chem. – Eur. J.*, 2019, **25**, 16246–16250; (o) A. Minotto, P. A. Haigh, G. Łukasiewicz, E. Lunedei, D. T. Gryko, I. Darwazeh and F. Cacialli, Visible light communication with efficient far-red/near-infrared polymer light-emitting diodes, *Light: Sci.*



*Appl.*, 2020, **9**, 70; (p) L. Wang, W. Jiang, S. Guo, S. Wang, M. Zhang, Z. Liu, G. Wang, Y. Miao, L. Yan, Y.-Y. Shao, Y.-W. Zhong, Z. Liu, D. Zhang, H. Fu and Y. Yao, Robust singlet fission process in strong absorption  $\pi$ -expanded diketopyrrolopyrroles, *Chem. Sci.*, 2022, **13**, 13907–13913.

12 J. J. Snellenburg, S. Laptenok, R. Seger, K. M. Mullen and I. H. M. van Stokkum, Glotaran: A Java-Based Graphical User Interface for the R Package TIMP, *J. Stat. Softw.*, 2012, **49**, 1–22.

13 (a) B. Valeur and M. N. Berberan-Santos, *Molecular Fluorescence: Principles and Applications*, Wiley-VCH, 2012, pp. 1–592; (b) J. R. Lakowicz, *Principles of Fluorescence Spectroscopy*, Springer, 2006, pp. 1–954; (c) J. B. Birks, *Photophysics of Aromatic Molecules*, Wiley-Interscience, 1970, pp. 1–704; (d) J. N. Demas, *Excited State Lifetime Measurements*, Academic Press, 1983, pp. 1–273; (e) C. Reichardt, *Solvents and Solvent Effects in Organic Chemistry*, Wiley-VCH, 2006, pp. 1–629.

14 (a) M. Di Donato, M. S. Centellas, A. Lapini, M. Lima, F. Avila, F. Santoro, C. Cappelli and R. Righini, Combination of Transient 2D-IR Experiments and Ab Initio Computations Sheds Light on the Formation of the Charge-Transfer State in Photoexcited Carbonyl Carotenoids, *J. Phys. Chem. B*, 2014, **118**, 9613–9630; (b) M. Di Donato, E. Ragnoni, A. Lapini, P. Foggi, R. G. Hiller and R. Righini, Femtosecond transient infrared and stimulated Raman spectroscopy shed light on the relaxation mechanisms of photo-excited peridinin, *J. Chem. Phys.*, 2015, **142**, 212409.

15 S. Doria, M. Di Donato, R. Borrelli, M. F. Gelin, J. Caram, M. Pagliai, P. Foggi and A. Lapini, Vibronic coherences in light harvesting nanotubes: unravelling the role of dark states, *J. Mater. Chem. C*, 2022, **10**, 7216–7226.

16 M. J. Frisch, *et al.*, *Gaussian 16 Revision B.01*, Gaussian Inc., Wallingford CT, 2016.

17 (a) S. I. Druzhinin, A. Demeter, V. A. Galievsky, T. Yoshihara and K. A. Zachariasse, Thermally Activated Internal Conversion with 4-(Dimethylamino)benzonitrile, 4-(Methylamino)-benzonitrile, and 4-Aminobenzonitrile in Alkane Solvents. No Correlation with Intramolecular Charge Transfer, *J. Phys. Chem. A*, 2003, **107**, 8075–8085; (b) K. Suzuki, A. Demeter, W. Kühnle, E. Tauer, K. A. Zachariasse, S. Tobita and H. Shizuka, Internal conversion in 4-substituted 1-naphthylamines. Influence of the electron donor/acceptor substituent character, *Phys. Chem. Chem. Phys.*, 2000, **2**, 981–991; (c) J. Hoche, A. Schulz, L. M. Dietrich, A. Humeniuk, M. Stolte, D. Schmidt, T. Brixner, F. Wurthner and R. Mitric, The origin of the solvent dependence of fluorescence quantum yields in dipolar merocyanine dyes, *Chem. Sci.*, 2019, **10**, 11013–11022.

