

Dalton Transactions

An international journal of inorganic chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. J. Clarke, N. Kelly, I. da Silva, K. M. Steele and H. Grievson, *Dalton Trans.*, 2025, DOI: 10.1039/D5DT00159E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Chemical and Electrochemical Lithiation of Van Der Waals Oxytelluride V_2Te_2O View Article Online
DOI: 10.1039/D5DT00159ENicola D. Kelly^{1,2,#}, Heather Grievson^{2,3}, Katherine M. Steele¹, Ivan da Silva⁴ and Simon J. Clarke^{1,2,*}

¹ Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford, OX1 3QR, UK.

² The Faraday Institution, Quad One, Harwell Campus, Didcot, OX11 0RA, UK.

³ School of Chemical, Materials and Biological Engineering, University of Sheffield, Sir Robert Hadfield Building, Sheffield, S1 3JD, UK.

⁴ ISIS Neutron and Muon Source, STFC, Rutherford Appleton Laboratory, Harwell Campus, Didcot, OX11 0QX, UK.

Present address: Jesus College, University of Cambridge, CB5 8BL, UK.

* simon.clarke@chem.ox.ac.uk



ABSTRACTView Article Online
DOI: 10.1039/D5DT00159E

Reversible lithium intercalation into the van der Waals phase V_2Te_2O , forming new phases $Li_xV_2Te_2O$ with x approaching 2, is reported using both chemical and electrochemical methods. The progress of each reaction was followed using powder X-ray diffraction and the crystal structure of the intercalated phase with $x = 1$, LiV_2Te_2O was refined using powder neutron diffraction. The intercalated Li ions occupy vacant pseudo-octahedral sites and the unit cell expands on reduction with no change in symmetry. The lithium ions can be removed chemically or electrochemically, making this the first known oxytelluride to undergo reversible lithium intercalation.



INTRODUCTION

Intercalation of alkali metal ions into layered transition-metal compounds is integral to the operation of rechargeable batteries. Much current materials chemistry research is focused on optimising these cathode materials for efficiency, cost, scale and reversibility considerations¹. A persistent problem is the high cost of cobalt, a key ingredient in many commercial Li-ion batteries with LiCoO₂ as the cathode. Ni and Mn substitution have been explored to mitigate this problem² but systems based on entirely different transition metal ions are also being developed, with a particular focus on iron-based oxides³, sulphates⁴ and phosphates⁵, since iron is a light and naturally very earth-abundant transition metal. These properties make iron-based cathodes attractive because of their high energy density and low cost respectively.

Vanadium is lighter than iron and more abundant in the continental crust than cobalt, nickel or copper⁶. Furthermore, it has many stable positive oxidation states (+2 to +5 inclusive), enabling multi-electron redox activity and hence a high theoretical capacity for rechargeable batteries^{7,8}. Recent studies on vanadium-based cathodes show promising results for polyanionic compounds, with reversible cycling observed for Li₂VO(SO₄)₂⁹, Na₄VO(PO₄)₂¹⁰, NaVPO₄F¹¹, ε-VOPO₄¹², and α- and β-VOSO₄¹³ among others.

Vanadium oxytelluride, V₂Te₂O, was first synthesised in 2018 by Ablimit *et al.* by reacting RbV₂Te₂O with H₂O at room temperature to extract the Rb⁺ ions¹⁴. It can similarly be produced by deintercalation of K⁺ ions from KV₂Te₂O¹⁵. V₂Te₂O consists of square planar layers of V³⁺ and O²⁻ ions, sandwiched between Te²⁻ layers which are weakly bonded in the *c* direction by van der Waals interactions. Similar van der Waals gaps are known to accept intercalated metal ions in layered tellurides including VTe₂¹⁶, NbTe₂ and TaTe₂¹⁷, Ti₂PTE₂ and ZrPTE₂¹⁸, Bi₂Te₃¹⁹, CrGeTe₃²⁰, Fe₃GeTe₂²¹ and Fe₅GeTe₂²², sometimes leading to dramatic physical property changes, such as an increase in the Curie temperature of CrGeTe₃ from 66 to 240 K with Na insertion. However, to our knowledge no such investigations have been carried out on oxytellurides, i.e., compounds containing both Te²⁻ and O²⁻ anions. Therefore, despite the presence of scarce, heavy and toxic Te atoms making it unviable for commercial battery applications, V₂Te₂O presents a worthwhile platform for investigating the fundamental chemistry and physics of lithium intercalation and property tuning via controlling the electron count. In this article we report the reductive intercalation of Li⁺ ions into V₂Te₂O both chemically, using n-butyllithium solution, and electrochemically, in cells where a Li metal anode is the Li source. The body-centred tetragonal symmetry of the host material is preserved upon insertion of Li⁺. The chemically lithiated products undergo oxidative deintercalation by air or water to re-form V₂Te₂O; our electrochemical studies also indicate the reversibility of Li insertion.



EXPERIMENTAL METHODS

View Article Online
DOI: 10.1039/D5DT00159E

Synthesis

All reagents and samples were treated as air- and moisture-sensitive and were therefore handled and manipulated in an argon-filled glovebox. The host compound V_2Te_2O was prepared from KV_2Te_2O as reported previously¹⁵. Briefly, KV_2Te_2O samples each of target mass 1.0 g were prepared from a stoichiometric mixture of K metal (99.95 %, Alfa Aesar) with powdered V_2O_5 (99.995 %, Alfa Aesar), V (99.95 %, Alfa Aesar) and Te (99.999 %, Alfa Aesar). The reagents were placed in alumina crucibles, vacuum-sealed into silica ampoules and heated to 300 °C for 12 h then 700 °C for 24 h with intermediate grinding. For each step, the ramp rates were 1 °C min⁻¹ on heating and the natural rate of the furnace on cooling. Subsequently, using a Schlenk line apparatus, degassed, deionised H_2O (50 cm³) was added to ~1 g KV_2Te_2O powder under a nitrogen atmosphere and stirred overnight at room temperature. Filtration, washing with tetrahydrofuran (2 × 20 cm³) and drying under dynamic vacuum yielded the target compound as a black powder.

Chemical lithiation was carried out on a Schlenk line. Typically, 0.1–0.2 g of V_2Te_2O powder was placed in a Schlenk flask under nitrogen and suspended in 5–10 cm³ of dry hexane. (The sample for neutron diffraction was synthesised in one batch on a larger scale, using 0.65 g of V_2Te_2O and 20 cm³ hexane.) An appropriate stoichiometric amount of n-butyllithium (1.6 M in hexanes, Sigma-Aldrich) was injected into the flask and the black suspension was stirred overnight at room temperature under a nitrogen atmosphere. The sample was then filtered, washed twice with hexane, and dried under dynamic vacuum to leave a fine black powder. Subsequent delithiation reactions were also carried out on the Schlenk line using water as the oxidant. 5–10 cm³ of deionised H_2O was introduced into a Schlenk flask containing $Li_xV_2Te_2O$ under nitrogen followed by stirring overnight, filtering, washing with tetrahydrofuran and drying under vacuum as described above.

Diffraction Measurements

Laboratory powder X-ray diffraction (PXRD) for phase identification was carried out at room temperature on either a PANalytical Empyrean or a Bruker Advance Eco D8 diffractometer, both using $CuK\alpha$ radiation, $\lambda = 1.541 \text{ \AA}$, and with the former instrument equipped with a monochromator to select only $CuK\alpha_1$ radiation. Powder samples were loaded onto a lightly greased glass slide, mounted in a custom-made airtight sample holder with Mylar® windows and measured in the range $5 \leq 2\theta \text{ (}^\circ\text{)} \leq 70$. Cycled cathode films were attached to the airtight holder using Kapton® tape around the edges, avoiding covering the area of material being illuminated by the X-ray beam.



Synchrotron PXRD for accurate and precise structural refinement was carried out at room temperature at the I11 beamline²³, Diamond Light Source, Didcot, UK, with a wavelength of $\lambda \approx 0.82$ Å (calibrated precisely at the start of each beamtime session using a Si standard). Samples were mixed 1:1 by volume with ground glass to reduce beam absorption and preferred orientation and packed into borosilicate capillaries of inner diameter 0.5 mm. Diffraction patterns were collected using a Mythen Position Sensitive Detector (PSD).

Time-of-flight powder neutron diffraction (PND) was carried out at room temperature on the GEM instrument at the ISIS Neutron and Muon Source, Oxfordshire, UK²⁴. The sample of mass 0.35 g was packed into a 6 mm vanadium canister and sealed with an indium gasket under inert atmosphere²⁵. Structure solution and Rietveld refinement²⁶ were carried out using TOPAS-Academic V7²⁷. VESTA²⁸ was used for crystal structure visualisation and production of figures.

Electrochemical Measurements

The active material (V_2Te_2O) was mixed with polyvinylidene fluoride (MTI Corporation) and carbon black C-ENERGY Super C65 (Imerys Graphite & Carbon) in a mass ratio of 8:1:1 and ground by hand for 15 minutes then made into a slurry with *N*-methyl pyrrolidone (Merck). The slurry was cast onto carbon-coated aluminium foil and dried at 80 °C in air then in an 80 °C vacuum oven for at least 16 h. CR2032 SS316 coin cells (Cambridge Energy Solutions Ltd) were assembled in an inert atmosphere glove box using 12 mm diameter cathodes cut from the cast film, 16 mm diameter separators of Whatman glass microfibre (Merck), 15.6 mm diameter lithium metal chips (Cambridge Energy Solutions Ltd) as the anode, and for the electrolyte 1 M LiPF₆ in ethylene carbonate and ethyl methyl carbonate, 3:7 v/v (Solvionic). Cyclic voltammetry was conducted at room temperature using a Biologic VMP-300 potentiostat and galvanostatic cycling was conducted at 25 °C using a MACCOR Series 4000. The cycling rate was $C/20$, where C is the theoretical capacity of the compound and $C/20$ means fully charging or discharging over 20 hours.

RESULTS AND DISCUSSION

Synthesis of V_2Te_2O

The host compound, produced from KV_2Te_2O using the soft-chemical method described above, was an air-stable black powder. The chemical yield was calculated using the mass of product; it varied between 75–85 %, reflecting some loss of powder upon filtration and extraction of the product from the Schlenk flask. Rietveld refinement of PXRD data indicated that V_2Te_2O crystallises in the body-centred tetragonal space group $I4/mmm$ as reported previously¹⁴. The crystal structure, shown in Figure 1(a), comprises planar V_2O layers in the *ab* plane, composed of vertex-linked OV_4 squares,



sandwiched between two layers of telluride ions so that each vanadium ion forms a *trans*-[VO₂Te₄] distorted octahedron. The resulting neutral Te–V₂O–Te slabs are stacked in a staggered manner along the *c* direction with van der Waals interactions between adjacent Te layers. A representative Rietveld refinement against synchrotron data is given in Figure 1(b); the refined lattice parameters for this sample were $a = 3.92667(2)$ Å, $c = 13.2181(2)$ Å. Samples reproducibly had high phase purity, containing less than 5 wt % each of the secondary phases KV₃Te₃O_{0.33}²⁹ and/or V₂O₃. These secondary phases are often produced during the initial ceramic synthesis and they remain in the sample after reaction with water.

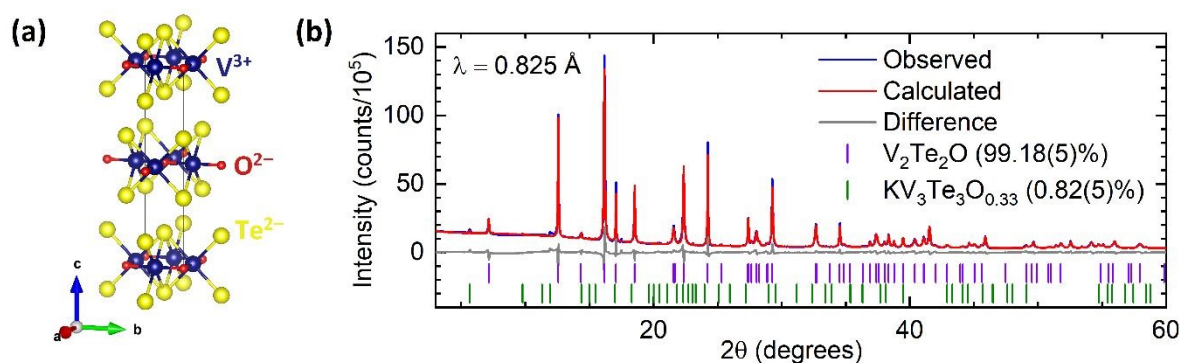


Figure 1: (a) Crystal structure of V₂Te₂O¹⁴ in tetragonal space group *I4/mmm*. (b) Rietveld refinement of synchrotron PXRD data for V₂Te₂O at room temperature. Blue – experimental data; red – calculated intensities; grey – difference pattern; tick marks – Bragg reflection positions for V₂Te₂O (purple) and KV₃Te₃O_{0.33} (green).

Chemical Lithiation and Powder X-ray Diffraction

V₂Te₂O was lithiated using solutions of *n*-butyllithium (nBuLi), resulting in an expansion of the unit cell in both *a* and *c* directions as observed by shifting of peaks in the PXRD patterns towards lower angles. This behaviour is consistent with the insertion of Li⁺ ions causing reduction of the vanadium ions and hence lengthening of the V–O and V–Te bonds. Figure 2 shows the resultant PXRD patterns for several different reaction stoichiometries. The patterns for the intercalated samples all have broader peaks than the parent material, indicating lower crystallinity, particularly in samples made with smaller amounts of nBuLi.



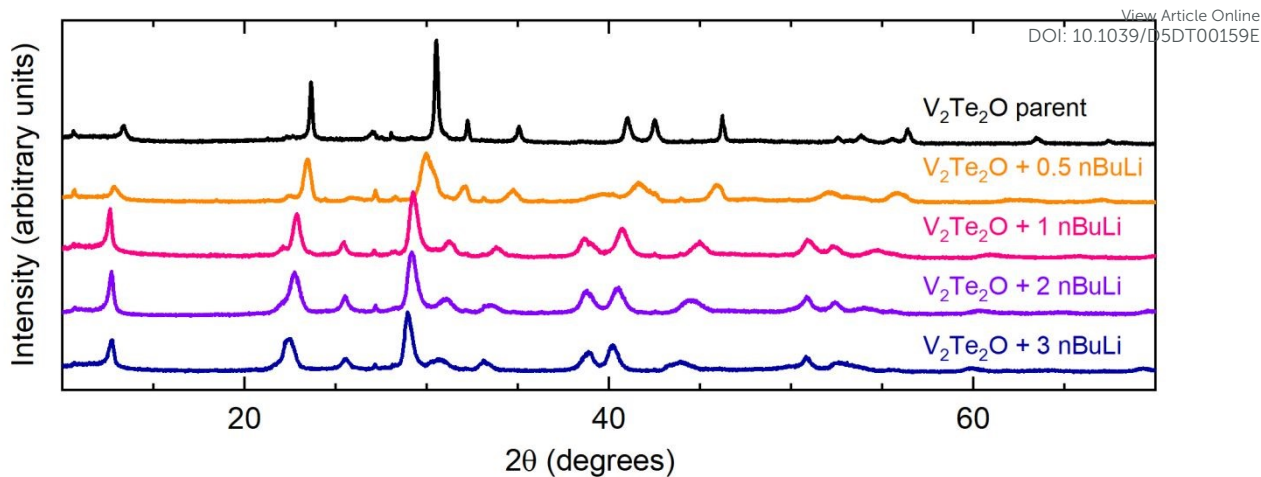


Figure 2: Laboratory PXRD patterns for the results of the reaction $V_2Te_2O + x \text{ nBuLi}$, where $0 \leq x \leq 3$ (top to bottom).

Rietveld refinement was carried out on PXRD data for all of the intercalated samples using the structure of V_2Te_2O ¹⁴ with an expanded unit cell. The positions of the V and O atoms at $(\frac{1}{2}, 0, 0)$ and $(0, 0, 0)$ respectively and the x and y coordinates of the Te atoms (special positions) at $(\frac{1}{2}, \frac{1}{2}, z_{Te})$ were kept fixed while the z-coordinate of Te was refined. Owing to their low X-ray scattering power, Li atoms were not included in the structural model for refinements against X-ray data. Figure 3 shows a representative Rietveld refinement of synchrotron PXRD data for an intercalated phase.

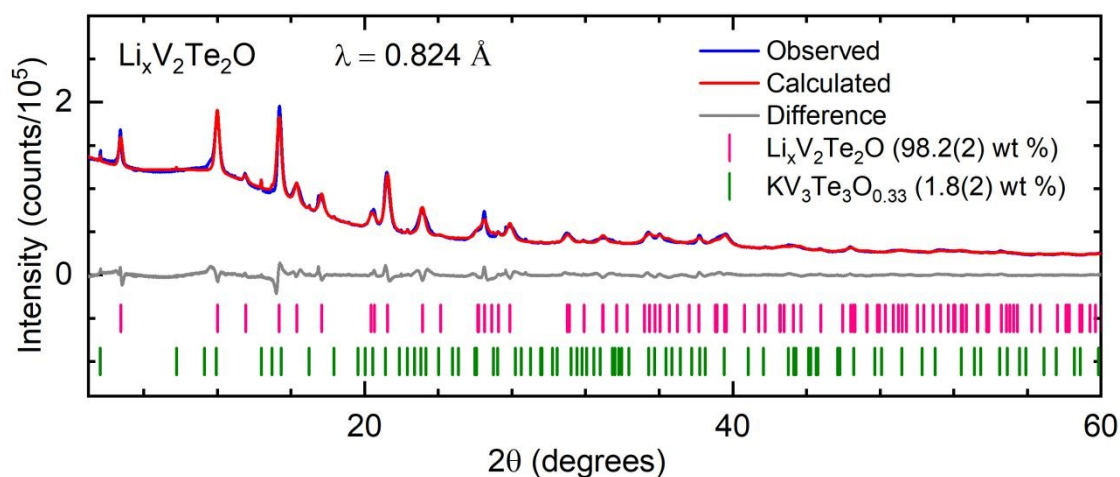


Figure 3: Rietveld refinement of synchrotron PXRD data for $Li_xV_2Te_2O$ (synthesised using 2 molar equiv. nBuLi) at room temperature. Blue – experimental data; red – calculated intensities; grey – difference pattern; tick marks – Bragg reflection positions for $Li_xV_2Te_2O$ (pink) and $KV_3Te_3O_{0.33}$ (green).

The refined lattice parameters from laboratory PXRD data for a series of intercalated phases are given in Table 1 and Figure 4, which plots the parameters relative to the parent material V_2Te_2O . The expansion in c increases upon reaction with up to 1 equivalent of nBuLi, then plateaus at approximately 5 %, whereas the expansion in a increases steadily until 3-4 molar equivalents of nBuLi



and then decreases again. We suggest that this behaviour is consistent with insertion of Li⁺ into the van der Waals gaps of V₂Te₂O, which consists of layers perpendicular to the *c* axis. The increase in *c*, corresponding to the interlayer spacing, would be approximately the same for any number of intercalated Li⁺ ions per formula unit above a certain threshold, because Li⁺ has a finite size. From the data, this threshold appears to be approximately 1-1.5 Li ions per formula unit of V₂Te₂O. By contrast, the *a* parameter could continue to increase as more Li⁺ ions are inserted because it depends on the V–O bond length, which will increase as vanadium is reduced. From the information in Figure 4, the limit of Li intercalation appears to be reached after reaction with 3-4 equivalents of *n*BuLi. After this point, the use of excess *n*BuLi favours the production of secondary impurity phases (evident in the powder diffraction patterns - see Fig. S3 in the ESI). This leaves less Li available to form the main Li_{*x*}V₂Te₂O phase, hence the subsequent decrease in the lattice parameters upon adding excess *n*BuLi (i.e. the behaviour of the lattice parameters shows that the intercalates obtained with excess *n*BuLi are actually less Li-rich than those obtained with a modest excess). We attempted to suppress side reactions by reducing the reaction time and/or temperature, but this resulted in no Li_{*x*}V₂Te₂O intercalate being formed.

Since the lowest non-zero stable oxidation state for vanadium is +2, V₂Te₂O is highly unlikely to accommodate insertion of more than two Li per formula unit, so there is likely an offset in the *x*-axis between the amount of BuLi added and the actual stoichiometry due to the side reactions. The limiting composition is discussed further below in the context of additional results from powder neutron diffraction and electrochemical cycling.



Table 1: Refined lattice parameters for chemically intercalated samples $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ from Rietveld refinement of laboratory PXRD data at room temperature. Space group: $I4/mmm$ (No. 139). Note that the number of moles of $n\text{BuLi}$ used in the reaction is not equal to the number of moles of Li intercalated into the host as discussed in the text.

| Sample code | Moles $n\text{BuLi}$ in reaction mixture | a (Å) | c (Å) | Volume (Å ³) |
|---|--|------------|-------------|--------------------------|
| $\text{V}_2\text{Te}_2\text{O}$ in literature ¹⁴ | - | 3.9282(1) | 13.2477(5) | 204.42(2) |
| $\text{V}_2\text{Te}_2\text{O}$ NDK235 | - | 3.9347(2) | 13.2371(10) | 204.93(3) |
| NDK304 | 0.5 | 3.9586(7) | 13.659(3) | 214.05(10) |
| NDK187 | 1.0 | 4.0280(7) | 13.952(4) | 226.36(10) |
| NDK305 | 1.5 | 4.0493(6) | 14.000(3) | 229.56(8) |
| NDK203 | 2.0 | 4.0761(5) | 13.975(3) | 232.19(8) |
| NDK260 ^a | 2.0 | 4.0803(10) | 13.987(4) | 232.9(2) |
| NDK204 | 3.0 | 4.1344(6) | 13.949(2) | 238.44(9) |
| NDK303 | 4.0 | 4.1392(9) | 13.947(4) | 239.0(2) |
| NDK341 | 5.0 | 4.0812(9) | 13.978(4) | 232.8(2) |
| NDK353 | 6.0 | 4.0488(8) | 13.910(4) | 228.0(2) |

^a sample used for neutron powder diffraction.

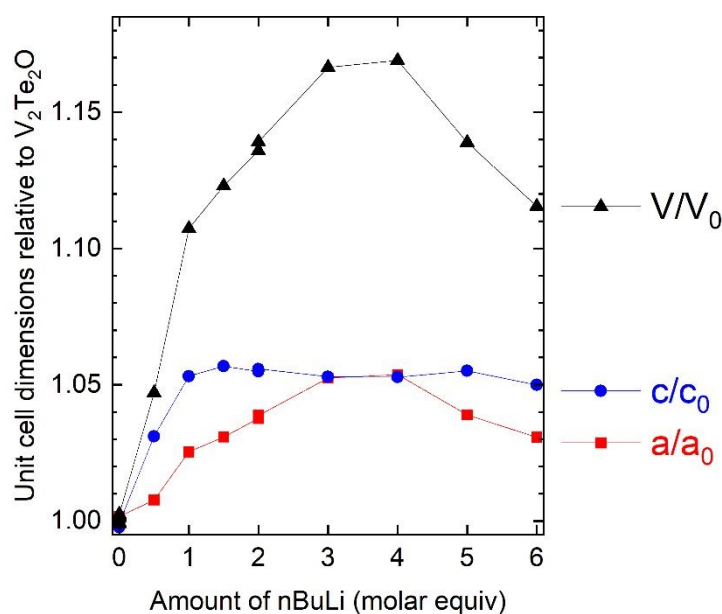


Figure 4: Refined lattice parameters for Li-intercalated samples, relative to the published parameters for $\text{V}_2\text{Te}_2\text{O}$ ¹⁴, as a function of reaction stoichiometry. Side reactions at high Li stoichiometries in the reaction result in less Li-rich intercalates with smaller cell volumes than the maximum.



Structure Solution using Powder Neutron Diffraction

View Article Online
DOI: 10.1039/D5DT00159E

The crystal structure of a 0.35 g sample of $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$, synthesised using 2 molar equivalents of nBuLi in the reaction, was investigated using time-of-flight PND at room temperature. We first examined the GEM bank 2 data because it has sufficient range in d-spacing to include the (002) reflection at $\sim 7 \text{ \AA}$ while also providing sufficient resolution for structural analysis. For the initial structural model we again used the published crystal structure of $\text{V}_2\text{Te}_2\text{O}$ ¹⁴ with an expanded unit cell; the initial lattice parameters were taken from PXRD analysis on the same sample and then refined against the neutron data using the Pawley method³⁰. In the subsequent Rietveld refinement there were discrepancies between the calculated and observed intensities for several Bragg reflections, with a noticeable overestimate of the (110) peak intensity. Li ions (Li has a negative scattering length³¹) were added to the model at sites (0, 0, zLi) where the starting value for zLi was chosen as 0.24 (approximately in the middle of the van der Waals gaps). Refining the Li and Te z-coordinates and the Li fractional site occupancy *occLi* (limited to values between 0 and 1 inclusive, where full occupancy would correspond to $x = 2$ in the formula $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$) resulted in an adequate fit with $z\text{Li} \sim 0.15$, $z\text{Te} \sim 0.14$, and *occLi* ~ 0.5 . We also attempted to model lithium in tetrahedral sites in the van der Waals gaps, ($\frac{1}{2}$, 0, $\frac{1}{4}$), but this did not fit the observed data as the Li occupancy refined to zero.

We subsequently carried out a combined Rietveld refinement on the data from GEM banks 2, 3 and 4. Owing to the low data quality, reflecting the small sample size, the high absorption cross-section of Li³¹ and the incoherent background from V, a single isotropic displacement parameter B_{iso} was refined for all 4 elements. The refined crystal structure and the bank 3 data are shown in Figure 5; the other banks are shown in the ESI (Figs S1 and S2). The refined structural parameters are given in Table 2.



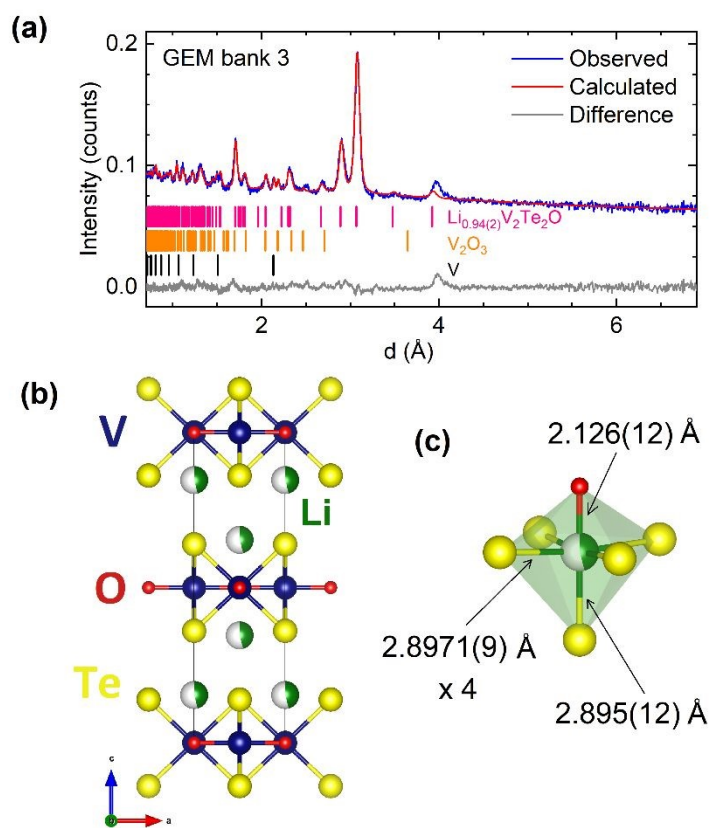


Figure 5: (a) Rietveld refinement of room temperature PND data for $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ measured on bank 3 of the GEM diffractometer at ISIS. Blue – experimental data; red – calculated intensities; grey – difference pattern; tick marks – Bragg reflection positions for $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ (pink), V_2O_3 (orange) and V sample container (black). (b) Structural model viewed perpendicular to the c axis. (c) Lithium-centred polyhedron.



Table 2: Structural parameters for $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ (sample NDK260) at room temperature, determined from a combined refinement of neutron time-of-flight powder diffraction data from GEM banks 2, 3 and 4. View Article Online
DOI: 10.1039/D5DT00159E

| Composition | | $\text{Li}_{0.94(2)}\text{V}_2\text{Te}_2\text{O}$ | | | | |
|---------------------|-------------|--|-----------------|-----------------|-----------------------------|--|
| Space group | | $I4/mmm$ (#139) | | | | |
| <i>a</i> (Å) | | 4.0887(6) | | | | |
| <i>c</i> (Å) | | 13.921(3) | | | | |
| Bank 2 | | $R_{\text{wp}} = 3.22 \%$, $\chi^2 = 1.10$ | | | | |
| Bank 3 | | $R_{\text{wp}} = 2.49 \%$, $\chi^2 = 2.31$ | | | | |
| Bank 4 | | $R_{\text{wp}} = 2.11 \%$, $\chi^2 = 3.14$ | | | | |
| Atom | Site | <i>x</i> | <i>y</i> | <i>z</i> | Fractional occupancy | B_{iso} (Å²) |
| Li | 4e | 0 | 0 | 0.1527(8) | 0.471(9) | 0.19(2) |
| V | 4c | ½ | 0 | 0 | 1 | |
| Te | 4e | ½ | ½ | 0.1394(2) | 1 | |
| O | 2a | 0 | 0 | 0 | 1 | |

The refinement (Figure 5(a) and ESI, Figs S1 and S2) includes two clear unindexed peaks at $d \sim 4.0$ and 2.5 \AA likely resulting from one or more impurity phases. The presence of impurities is perhaps unsurprising given the excess of nBuLi used compared with the final stoichiometry, with the remaining nBuLi presumably having been used up in side reactions. Furthermore, a peak at 4 \AA is clearly visible in laboratory and synchrotron X-ray data for the majority of our nBuLi-intercalated samples (see e.g. Figure 3 at $2\theta \sim 10^\circ$) and its intensity relative to the main phase increases with increasing amounts of nBuLi (ESI, Fig. S3). However, the additional intensity could not be fitted by any appropriate binary or ternary compound in the Inorganic Crystal Structure Database (ICSD). We also attempted to fit a second $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ phase with either an expanded body-centred structure, or a primitive tetragonal structure similar to that of $\text{KV}_2\text{Te}_2\text{O}$ ¹⁵, but neither model was able to account satisfactorily for the impurity peaks.

The intercalated lithium ions occupy pseudo-octahedral sites (Figure 5(c)) where each Li ion is bonded to one oxide anion at a distance of $2.13(2) \text{ \AA}$ and five telluride anions at distances of $2.8971(9) \text{ \AA}$ (equatorial) and $2.90(2) \text{ \AA}$ (axial). These values are consistent with Li–O and Li–Te bond lengths in octahedral environments in compounds reported in the literature, e.g. 2.12 \AA in LiVO_2 ³² and 2.93 \AA in LiCrTe_2 .³³ This site is also chemically reasonable, considering lithium's strong affinity for oxygen according to HSAB theory.



The refined site occupancy for Li of 0.471(9) corresponds to the composition $\text{Li}_{0.94(2)}\text{V}_2\text{Te}_2\text{O}$ and an average vanadium oxidation state of +2.53, close to the oxidation states observed in the related 1221 phases $A_{1-x}\text{V}_2\text{Te}_2\text{O}$ ($A = \text{K}, \text{Rb}, \text{Cs}$)^{15,34}. The refined bond length for V–O (equivalent to $a/2$) in our sample is 2.0443(4) Å; for comparison, the V–O bond lengths for 6-coordinate vanadium(III) are 1.968 Å in V_2O_3 ³⁵ and 1.9641(1) Å in $\text{V}_2\text{Te}_2\text{O}$ ¹⁴, whereas the vanadium(II) oxide VO has bond lengths of 2.06 Å³⁶. Therefore, our result is consistent with an average vanadium oxidation state between +2 and +3 in $\text{Li}_{0.94}\text{V}_2\text{Te}_2\text{O}$. Furthermore, the V–Te bond length from our neutron refinement is 2.8183(15) Å, which is very similar to the 2.798 Å of $\text{Rb}_{1-x}\text{V}_2\text{Te}_2\text{O}$ with almost the same vanadium oxidation state³⁴.

Chemical Delithiation

Lithium ions could be extracted from $\text{Li}_x\text{V}_2\text{Te}_2\text{O}$ upon exposure to moist air. A sample with $x = 0.94$, as determined by powder neutron diffraction, was investigated by first carrying out a 5-minute laboratory PXRD scan over a narrow 2θ range, 10–15°, to encompass only the (002) reflection. The airtight lid of the sample holder was then removed for 2 seconds to introduce air, the lid was replaced and a further nine such scans were collected in succession. Figure 6 shows the background-subtracted data which demonstrate a shift to higher angles (smaller d-spacing) with increasing time, indicating the removal of Li^+ ions and re-oxidation of vanadium. After 24 hours the sample had fully decomposed with $\text{V}_2\text{Te}_2\text{O}$ and elemental Te evident in the powder pattern (ESI, Fig. S4). The lattice parameters of the parent, lithiated and fully delithiated phases are given in Table 3.


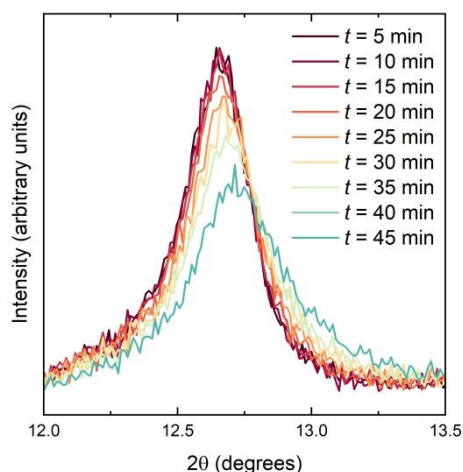


Figure 6: PXRD data (background subtracted) for $\text{Li}_{0.94}\text{V}_2\text{Te}_2\text{O}$ upon exposure to moist air.

Lithium ions could also be extracted using water under anaerobic conditions. Small bubbles of gas were released during the reaction. Laboratory PXRD analysis on the product (ESI, Fig. S5) indicated that $\text{V}_2\text{Te}_2\text{O}$ had been re-formed, with the lattice parameters of the main $I4/mmm$ phase decreasing



again to values matching those of the initial parent compound (Table 3). Therefore, the proposed equation for Li deintercalation is:



with LiOH being water-soluble and hence not present in the product PXRD pattern. Finally, reactions with a more oxidising solution of iodine in acetonitrile led to complete decomposition and oxidation of telluride ions to elemental tellurium.

Table 3: Lattice parameters for samples of $\text{V}_2\text{Te}_2\text{O}$ before and after chemical lithiation and subsequent delithiation, obtained from Rietveld refinement of room-temperature laboratory PXRD data.

| Sample code | Description | a (Å) | c (Å) |
|-------------|--|------------|-----------|
| NDK259 | Original parent compound | 3.9358(3) | 13.247(2) |
| NDK260 | Lithiated using BuLi \rightarrow $\text{Li}_{0.94}\text{V}_2\text{Te}_2\text{O}^a$ | 4.0803(10) | 13.987(4) |
| NDK260A | Delithiated in air | 3.9264(3) | 13.225(2) |
| NDK260B | Delithiated using H_2O | 3.9376(9) | 13.248(4) |

^a Composition determined from powder neutron diffraction.

Electrochemical Characterisation

Cyclic voltammetry data were collected from samples of $\text{V}_2\text{Te}_2\text{O}$ in the range 1.0-3.7 V, as shown in Figure 7(a). On sweeping the potential down in the first cycle, two reduction maxima were observed, the first between 1.7 and 1.4 V and the second between 1.4 and 1.0 V. Two distinct oxidation features were observed upon increasing the potential again at 1.2 to 1.8 V and 1.8 to 2.1 V. Upon cycling, the reduction features persisted (with gradually decreasing magnitude) but the oxidation features quickly became broader and by the fourth cycle had merged into a single wide feature situated between 1.2 and 2.5 V.

We assign the observed redox features to the reversible insertion and extraction of Li^+ ions, as observed by chemical reduction and reoxidation. The broadening of the oxidation maxima and the overall decline in magnitude of both the reductive and oxidative processes are attributed to gradual decomposition of the cathode material. The loss of electrochemical activity upon cycling is also visible in the discharge-charge cycling data, Figure 7(b,c). The initial discharge capacity of 180 mAh g^{-1} rapidly declines by more than 75 % over the first 15 cycles then continues to tail off more slowly.



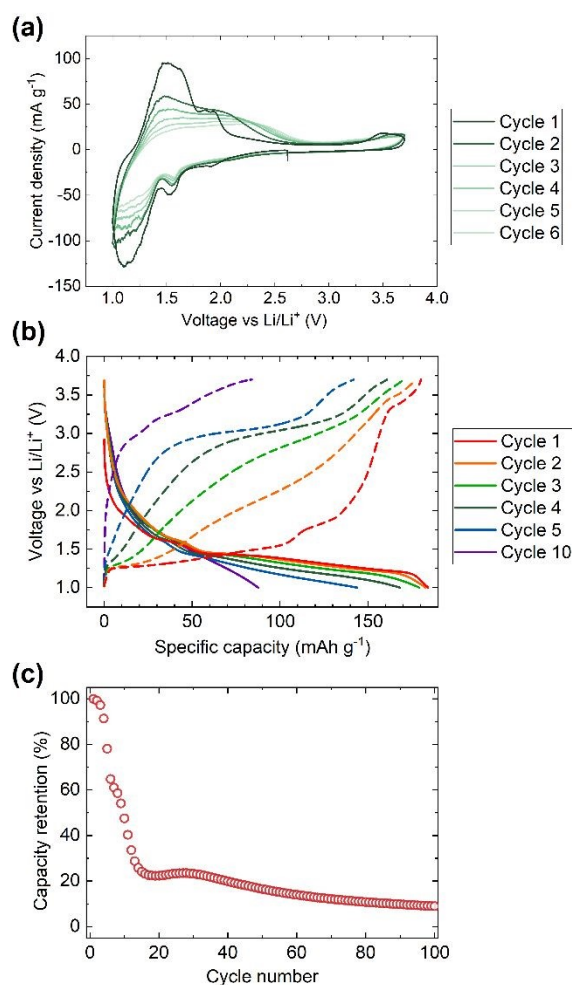


Figure 7: Electrochemical data for V_2Te_2O . (a) cyclic voltammetry data, (b) discharge-charge cycling profiles, and (c) capacity data were collected in the range 1.0 to 3.7 V.

Ex-situ PXRD was carried out on several cathode films after stopping the current and disassembling cells under argon at different points in the discharge-charge cycling profiles. The results are given in Table 4 and Figure 8.



Table 4: Results of ex-situ PXRD analysis on cycled cathode materials.

| Colour code in Figure 8 | Cycling state | a (Å) | c (Å) |
|-------------------------|--|-----------|-----------|
| Red | Open circuit voltage (OCV), rest for 2 h | 3.9261(4) | 13.227(2) |
| Orange | OCV, discharge to 1.4 V | 3.9255(5) | 13.223(2) |
| Green | OCV, discharge to 1.3 V | 3.937(5) | 13.27(2) |
| Light blue | OCV, discharge to 1.2 V | 4.007(3) | 13.93(2) |
| Dark blue | OCV, discharge to 1.1 V | 4.057(6) | 14.02(2) |
| Purple | OCV, discharge to 1.0 V | 4.106(2) | 13.959(9) |
| Black | 1 discharge-charge cycle (1.0–3.7 V) | 3.9256(4) | 13.227(2) |
| Grey | 10 discharge-charge cycles (1.0–3.7 V) | 3.9158(6) | 13.211(2) |

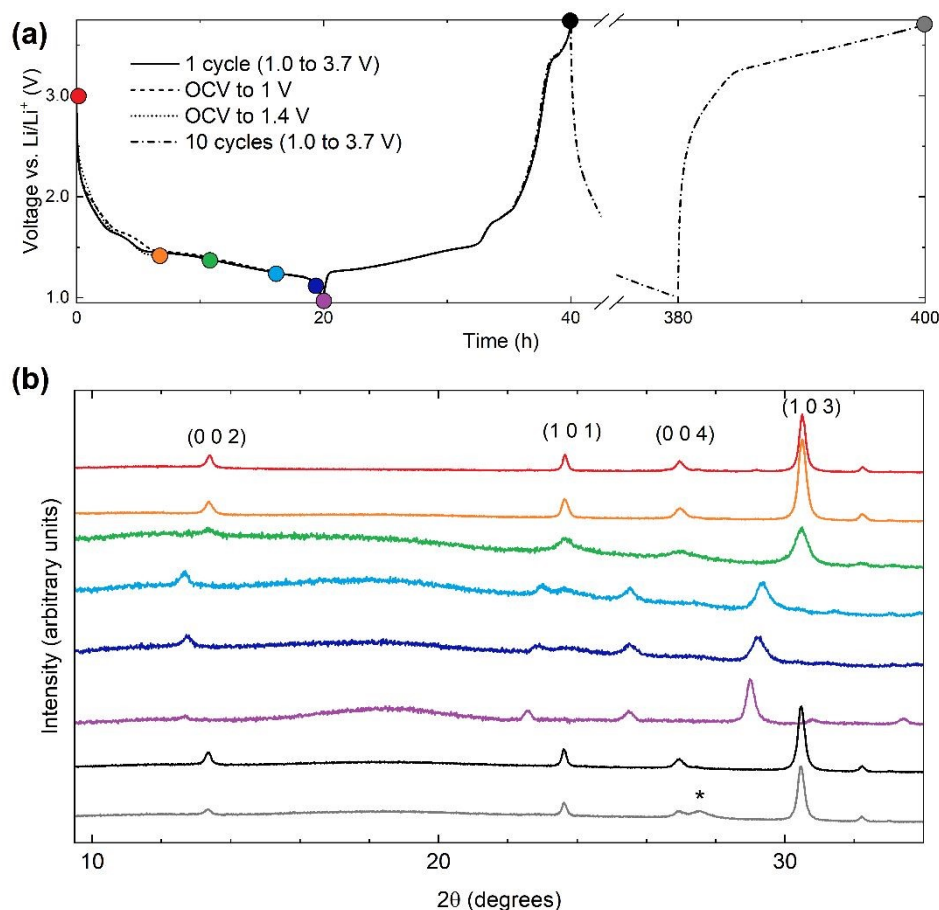


Figure 8: (a) selected electrochemical charge-discharge cycling curves, (b) ex situ PXRD patterns with colours corresponding to the coloured circles in (a). The asterisk * indicates the main Bragg peak for elemental tellurium.



The production of elemental Te (~ 27 wt % after only 10 cycles, indicated by the * in Figure 8(b)) indicates the oxidative decomposition of V_2Te_2O upon cycling via oxidation of telluride. The Te peak at $2\theta = 27.5^\circ$ is absent after the first discharge (purple dataset) and only appears after the first charge (black dataset), indicating that Te is produced in the oxidative part of the cycle. This is consistent with electronic structure calculations of the related oxytellurides $Rb_{0.8}V_2Te_2O$ and V_2Te_2O ,^{14,34} which showed that the Te 5p bands are around 2 eV below the Fermi level and thus accessible at the voltages used here. The PXRD measurements also show that the reversible insertion and removal of lithium occurs mainly in the plateau between 1.4 and 1.0 V upon discharge and charge respectively.

Lattice parameters were obtained from Rietveld refinement of the *ex situ* cathode XRD data and have been plotted in Figure 9. Visual comparison of these data with those in Figure 4 show that, while the existing data does not allow the *x* axes to be calibrated quantitatively to each other, the electrochemical and chemical intercalation routes show similar behaviour in terms of both the relative rates of increase of *a* and *c* and their maximum values.

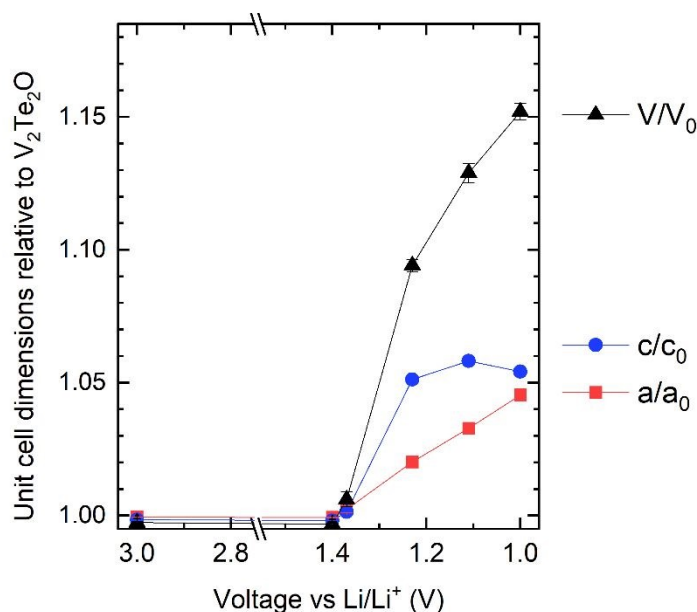


Figure 9: Refined lattice parameters for the electrochemically intercalated materials (cycled cathodes), relative to the published parameters for V_2Te_2O ¹⁴, as a function of the state of charge.

Insertion of 1 Li^+ per V_2Te_2O has a theoretical specific capacity of 72 mAh g^{-1} so the initial capacity of 180 mAh g^{-1} would correspond to ~ 2.5 Li. However, there are no changes to the V_2Te_2O lattice parameters between the open circuit voltage and 1.4 V (Table 4), which suggests that the first part of the cycle involves alternative reactions such as Li insertion into the conductive carbon (used to increase conductivity of the cathode) or irreversible conversion-type reactions. Figure 7(b) shows that this would account for approximately the first 50 mAh g^{-1} of the capacity, leaving only around 1.8 Li to be inserted into the active material itself. This would tally with the slower rate of capacity



fade after the capacity has dropped to $\sim 40 \text{ mAh g}^{-1}$: the overall shape of the plot in Figure 7(c) could represent $\text{V}_2\text{Te}_2\text{O}/\text{Li}$ cycling with a rapid decline in capacity down to zero by 20 cycles, superimposed on a slower decline in the capacity from other parts of the cell.

Discussion of the Lithium Composition: Comparisons and Limitations

In the chemical intercalation route, the refined Li occupancy for the sample analysed by PND was lower than expected for the amount of BuLi added, e.g. $\text{V}_2\text{Te}_2\text{O} + 2 \text{ nBuLi}$ produced a refined composition $\text{Li}_{0.94}\text{V}_2\text{Te}_2\text{O}$. We attribute this observation to side reactions which use up one or more molar equivalents of nBuLi. Full occupancy of the Li site would correspond to a composition of $\text{Li}_2\text{V}_2\text{Te}_2\text{O}$ and reduction to V^{2+} . The fact that the maximum cell volume and a lattice parameter were observed when 3 or 4 molar equivalents of BuLi were used in the chemical synthesis (i.e. excesses of Li compared with the availability of intercalation sites and reasonable vanadium redox chemistry (Figure 4)), confirms this. In the electrochemical intercalation route, the initial invariance of the lattice parameters of the oxytelluride phase at early stages of discharge suggests side reactions, perhaps related to the conductive carbon in the cathode mixture. The current passed in the later portion of the discharge, during which there is a change in the lattice parameters, corresponds to the insertion of 1.8 moles of Li per mole of $\text{V}_2\text{Te}_2\text{O}$ on discharge to 1.0 V, and accordingly the increase in cell volume of the most lithiated phase, formed by discharging to 1.0 V (purple dataset in Figure 8) is about 10 % less than the maximum found using excess nBuLi in the chemical route, consistent with the chemical route giving a limiting composition of $\text{Li}_2\text{V}_2\text{Te}_2\text{O}$. The lattice parameters derived from cathodes at intermediate states of charge map well onto those of the chemically intercalated samples made with 0.5–2 equiv. nBuLi.

The low weight of Li and the fact that the variation in cell volume may not be linear with composition over the full compositional range means that it is not feasible to calibrate the Li contents directly between the chemically and electrochemically intercalated routes without an extensive neutron diffraction study on several different samples, including large samples of electrochemically cycled materials, which is beyond the scope of the present work. However, our assumption of $\sim 50 \text{ mAh g}^{-1}$ of initial capacity from side processes would suggest ~ 1.8 Li as the limiting composition upon electrochemical discharge vs Li/Li^+ down to 1.0 V, and the chemical route is able to access slightly higher Li contents based on the slightly larger maximum unit cell volume.

A composition of $\text{Li}_2\text{V}_2\text{Te}_2\text{O}$ would correspond to an average vanadium oxidation state of +2 which is the lowest stable non-zero oxidation state. However, in other compounds containing the same



[M_2Q_2O] layer, where M is a 3d transition metal and Q is a chalcogenide (S, Se, Te) or pnictide (As, Sb, Bi) ion, we note that there is a trend for early transition metals to favour higher oxidation states than later transition metals, in line with the trend in ionisation energies across the series. For example, the Ti oxypnictides (such as $BaTi_2Sb_2O$) all contain Ti^{3+} ³⁷ and the Ti and V oxychalcogenides exhibit metal oxidation states between +2.5 and +3¹⁵; the chromium oxyarsenide $Sr_2CrO_2Cr_2OAs_2$ contains Cr^{3+} in the [M_2Q_2O] layer³⁸. However, for the later transition metals Mn, Fe and Co there are a number of known oxychalcogenides which all contain M^{2+} in the [M_2Q_2O] layer.^{39–42} In our sample probed by neutron diffraction, with a relatively low level of impurities, the vanadium ions reached a minimum oxidation state of about +2.5. Further reduction is possible chemically or electrochemically based on the lattice parameters in Figure 4 and Figure 9, however the increasing prevalence of side products on further reduction may be a consequence of the difficulty in attaining the V^{2+} oxidation state. Given the uncertainties in the refined parameters and the evident presence of side reactions, additional neutron diffraction experiments on samples made with a larger excess of nBuLi would be required to confirm whether the proposed limiting composition of $Li_2V_2Te_2O$ can be attained. Furthermore, neutron diffraction on an *in situ* electrochemical cell would be invaluable because it would provide an accurate limiting composition for the electrochemical intercalation route, but could also act as a calibration curve between Li content and lattice parameters.

CONCLUSIONS

The van der Waals layered oxytelluride V_2Te_2O was investigated as a host for lithium intercalation reactions. Chemical intercalation using n-BuLi resulted in the formation of $Li_xV_2Te_2O$ with an expanded unit cell but no significant change to the host crystal structure. Powder neutron diffraction was used to determine the composition and crystal structure of a representative sample, in which Li occupies a six-coordinate site bonded to one oxide and five telluride anions. This sample had $x = 0.94(2)$, and examination of powder X-ray diffraction data for various samples suggests that the maximum extent of chemical lithiation via this route approaches $x = 2$. The intercalated Li^+ ions could subsequently be fully deintercalated using air or water. Electrochemical investigations, including *ex situ* structural analysis at different points during the cycling process, reinforce the conclusion of reversible lithiation of V_2Te_2O (again up to a limiting composition, here $x \sim 1.8$ when the cell is discharged to 1.0 V) albeit with significant capacity fade on cycling owing to gradual decomposition which includes oxidation of telluride ions to elemental Te during the charging process. Future work will focus on *in situ* and *ex situ* X-ray and neutron diffraction experiments in order to calibrate the Li content and lattice parameters across both the chemical and electrochemical intercalation routes with changes in physical properties as a function of vanadium oxidation state.



AUTHOR CONTRIBUTIONS

N. D. K. devised the project, carried out the synthesis, the crystallographic characterisation and the physical property measurements. H. G. performed the electrochemical cycling experiments and analysis and K. M. S. performed powder diffraction experiments on the electrochemically synthesised samples. I. da S. collected and processed the powder neutron diffraction data. S. J. C. directed the research and provided funding and resources. N. D. K. wrote the paper with input from S. J. C. and the other authors.

CONFLICT OF INTEREST

There are no conflicts of interest to declare

ACKNOWLEDGMENTS

This work was supported by the Faraday Institution project FutureCat (FIRG017), the UK EPSRC (EP/T027991/1 and EP/R042594/1) and the Diamond Light Source (Block Allocation Grant CY32893). Experiments at the ISIS Neutron and Muon Source were supported by a beamtime allocation XB2390120²⁵ from the Science and Technology Facilities Council. We thank S. J. Cassidy and J. I. Murrell for assistance on the I11 beamline, R. D. Smyth for packing the neutron sample, and R. Wernert for assistance in electrochemical interpretation. N. D. K. gratefully acknowledges support from a Jesus College Research Fellowship.

SUPPLEMENTAL MATERIAL

Electronic supplemental information (ESI) is available which contains PND refinements from other diffractometer banks, PXRD evidence for the secondary phase produced in chemical intercalations, PXRD refinements after the chemical deintercalation reactions using air and water, and magnetometry measurements on the chemically intercalated samples.



REFERENCES

- 1 S. G. Booth, A. J. Nedoma, N. N. Anthonisamy, P. J. Baker, R. Boston, H. Bronstein, S. J. Clarke, E. J. Cussen, V. Daramalla, M. De Volder, S. E. Dutton, V. Falkowski, N. A. Fleck, H. S. Geddes, N. Gollapally, A. L. Goodwin, J. M. Griffin, A. R. Haworth, M. A. Hayward, S. Hull, B. J. Inkson, B. J. Johnston, Z. Lu, J. L. MacManus-Driscoll, X. Martínez De Irujo Labalde, I. McClelland, K. McCombie, B. Murdock, D. Nayak, S. Park, G. E. Pérez, C. J. Pickard, L. F. J. Piper, H. Y. Playford, S. Price, D. O. Scanlon, J. C. Stallard, N. Tapia-Ruiz, A. R. West, L. Wheatcroft, M. Wilson, L. Zhang, X. Zhi, B. Zhu and S. A. Cussen, *APL Mater.*, 2021, **9**, 109201.
- 2 P. Mukherjee, J. A. M. Paddison, C. Xu, Z. Ruff, A. R. Wildes, D. A. Keen, R. I. Smith, C. P. Grey and S. E. Dutton, *Inorg. Chem.*, 2021, **60**, 263–271.
- 3 X. Martínez De Irujo Labalde, M. Y. Lee, H. Grievson, J.-M. Mortimer, S. G. Booth, E. Suard, S. A. Cussen and M. A. Hayward, *Inorg. Chem.*, 2024, **63**, 1395–1403.
- 4 L. Lander, J. M. Tarascon and A. Yamada, *Chem. Rec.*, 2018, **18**, 1394–1408.
- 5 M. Hadouchi, T. Koketsu, Z. Hu and J. Ma, *Batter. Energy*, 2022, **1**, 20210010.
- 6 S. R. Taylor, *Geochim. Cosmochim. Acta*, 1964, **28**, 1273–1285.
- 7 R. C. Vincent, P. Vishnoi, M. B. Preefer, J. X. Shen, F. Seeler, K. A. Persson and R. Seshadri, *ACS Appl. Mater. Interfaces*, 2020, **12**, 48662–48668.
- 8 Z. Lv, M. Ling, M. Yue, X. Li, M. Song, Q. Zheng and H. Zhang, *J. Energy Chem.*, 2021, **55**, 361–390.
- 9 M. Sun, G. Rousse, M. Saubanère, M. L. Doublet, D. Dalla Corte and J. M. Tarascon, *Chem. Mater.*, 2016, **28**, 6637–6643.
- 10 W. Deriouche, E. Anger, M. Freire, A. Maignan, N. Amdouni and V. Pralong, *Solid State Sci.*, 2017, **72**, 124–129.
- 11 Y. Lu, S. Zhang, Y. Li, L. Xue, G. Xu and X. Zhang, *J. Power Sources*, 2014, **247**, 770–777.
- 12 C. Siu, I. D. Seymour, S. Britto, H. Zhang, J. Rana, J. Feng, F. O. Omenya, H. Zhou, N. A. Chernova, G. Zhou, C. P. Grey, L. F. J. Piper and M. S. Whittingham, *Chem. Commun.*, 2018, **54**, 7802–7805.
- 13 W. Deriouche, E. Anger, N. Amdouni and V. Pralong, *Chim. Techno Acta*, 2019, **6**, 31–36.



- 14 A. Ablimit, Y. L. Sun, E. J. Cheng, Y. Bin Liu, S. Q. Wu, H. Jiang, Z. Ren, S. Li and G. H. Cao, *Inorg. Chem.*, 2018, **57**, 14617–14623. View Article Online
DOI: 10.1039/D8DT00159E
- 15 N. D. Kelly and S. J. Clarke, *J. Solid State Chem.*, 2023, **327**, 124276.
- 16 R. Guzmán, J. Morales and J. L. Tirado, *J. Mater. Chem.*, 1993, **3**, 1271–1274.
- 17 D. W. Murphy, F. J. DiSalvo, G. W. Hull and J. V. Waszczak, *Inorg. Chem.*, 1976, **15**, 17–21.
- 18 T. Yajima, M. Koshiko, Y. Zhang, T. Oguchi, W. Yu, D. Kato, Y. Kobayashi, Y. Orikasa, T. Yamamoto, Y. Uchimoto, M. A. Green and H. Kageyama, *Nat. Commun.*, 2016, **7**, 13809.
- 19 Z. Ding, S. K. Bux, D. J. King, F. L. Chang, T.-H. Chen, S.-C. Huang and R. B. Kaner, *J. Mater. Chem.*, 2009, **19**, 2588.
- 20 S. Khan, E. S. Y. Aw, L. A. V. Nagle-Cocco, A. Sud, S. Ghosh, M. K. B. Subhan, Z. Xue, C. Freeman, D. Sagkovits, A. Gutiérrez-Llorente, I. Verzhbitskiy, D. M. Arroo, C. W. Zollitsch, G. Eda, E. J. G. Santos, S. E. Dutton, S. T. Bramwell, C. A. Howard and H. Kurebayashi, *Adv. Mater.*, 2024, **2024**, 2400270.
- 21 D. Weber, A. H. Trout, D. W. McComb and J. E. Goldberger, *Nano Lett.*, 2019, **19**, 5031–5035.
- 22 P. A. Hyde, University of Oxford, 2023.
- 23 S. P. Thompson, J. E. Parker, J. Potter, T. P. Hill, A. Birt, T. M. Cobb, F. Yuan and C. C. Tang, *Rev. Sci. Instrum.*, 2009, **80**, 075107.
- 24 A. C. Hannon, *Nucl. Instruments Methods Phys. Res. A*, 2005, **551**, 88–107.
- 25 S. J. Clarke, *STFC ISIS Neutron Muon Source*, <https://doi.org/10.5286/ISIS.E.RB2390120-1>.
- 26 H. M. Rietveld, *J. Appl. Crystallogr.*, 1969, **2**, 65–71.
- 27 A. A. Coelho, *J. Appl. Crystallogr.*, 2018, **51**, 210–218.
- 28 K. Momma and F. Izumi, *J. Appl. Crystallogr.*, 2011, **44**, 1272–1276.
- 29 Z. Guo, F. Sun, D. Puggioni, Y. Luo, X. Li, X. Zhou, D. Y. Chung, E. Cheng, S. Li, J. M. Rondinelli, W. Yuan and M. G. Kanatzidis, *Chem. Mater.*, 2021, **33**, 2611–2623.
- 30 G. S. Pawley, *J. Appl. Crystallogr.*, 1981, **14**, 357–361.
- 31 V. F. Sears, *Neutron News*, 1992, **3**, 26–37.
- 32 L. P. Cardoso, D. E. Cox, T. A. Hewston and B. L. Chamberland, *J. Solid State Chem.*, 1988, **72**,



234–243.

View Article Online
DOI: 10.1039/D5DT00159E

- 33 S. Kobayashi, H. Ueda, C. Michioka and K. Yoshimura, *Inorg. Chem.*, 2016, **55**, 7407–7413.
- 34 A. Ablimit, Y. L. Sun, H. Jiang, S. Q. Wu, Y. Bin Liu and G. H. Cao, *Phys. Rev. B*, 2018, **97**, 214517.
- 35 C. E. Rice and W. R. Robinson, *J. Solid State Chem.*, 1977, **21**, 145–154.
- 36 H. Hartmann and W. Mässung, *Zeitschrift für Anorg. und Allg. Chemie*, 1951, **266**, 98–104.
- 37 T. Yajima, *Condens. Matter*, 2017, **2**, 4.
- 38 B. C. Sheath, X. Xu, P. Manuel, J. Hadermann, M. Batuk, J. O’Sullivan, R. S. Bonilla and S. J. Clarke, *Inorg. Chem.*, 2022, **61**, 12373–12385.
- 39 H. Kabbour, E. Janod, B. Corraze, M. Danot, C. Lee, M. H. Whangbo and L. Cario, *J. Am. Chem. Soc.*, 2008, **130**, 8261–8270.
- 40 D. G. Free, N. D. Withers, P. J. Hickey and J. S. O. Evans, *Chem. Mater.*, 2011, **23**, 1625–1635.
- 41 S. Song, Y. Lin, B. Li, S. Wu, Q. Zhu, Z. Ren and G. Cao, *Phys. Rev. Mater.*, 2022, **6**, 055002.
- 42 S. J. Song, J. Y. Lu, Q. Q. Zhu, Z. Ren and G. H. Cao, *J. Phys. Chem. Solids*, 2023, **181**, 111469.



Re: Chemical and Electrochemical Lithiation of Van Der Waals Oxytelluride V_2Te_2O

Nicola D. Kelly, Heather Grievson, Katherine M. Steele, Ivan da Silva and Simon J. Clarke

Submission to *Dalton*

View Article Online
DOI: 10.1039/D5DT00159E

The data used in this publication are available from the author on reasonable request.

The Neutron powder diffraction data are available through the following link.

<https://doi.org/10.5286/ISIS.E.RB2390120-1>

