

# EES Solar

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: N. Daem, M. Charlier, G. Spronck, P. Colson, R. Cloots and J. Dewalque, *EES Sol.*, 2025, DOI: 10.1039/D4EL00036F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Broader context statement

View Article Online  
DOI: 10.1039/D4EL00036F

Antimony sulfide ( $\text{Sb}_2\text{S}_3$ ) is a promising material for photovoltaics due to its low toxicity, suitable bandgap (1.4–1.8 eV), high absorption coefficient ( $\sim 10^5 \text{ cm}^{-1}$ ), and defect tolerance. This study is among the first to explore how the choice of antimony precursor and electron transport layer architecture influence the performance of  $\text{Sb}_2\text{S}_3$ -based solar cells. Comparing  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  as precursors revealed differences in film coverage, uniformity, and crystalline orientation, with  $\text{SbCl}_3$  yielding a more favorable bandgap (1.65 eV) and better charge transfer due to its [hk1] orientation. Additionally, the incorporation of mesoporous  $\text{TiO}_2$  for charge transport was investigated, but the architecture showed lower efficiency due to crystal misorientation ([hk0]). These findings highlight the critical role of precursor selection, bandgap alignment, and crystalline orientation in device performance. As a pioneering study, it provides a valuable foundation for further research aimed at optimizing  $\text{Sb}_2\text{S}_3$  for efficient and sustainable solar energy solutions.



# Spin-coating processing of oriented Sb<sub>2</sub>S<sub>3</sub> layer for PV applications: effect of the precursors and the device architecture

View Article Online  
DOI: 10.1039/D4EL00036F

Nathan Daem,<sup>1</sup> Marie-Julie Charlier,<sup>1</sup> Gilles Spronck,<sup>1</sup> Pierre Colson,<sup>1</sup> Rudi Cloots<sup>1,\*</sup> and Jennifer Dewalque<sup>1</sup>

<sup>1</sup> Group of Research in Energy and Environment from Materials (GREENMat), CESAM Research Unit, Chemistry Department, University of Liège, Allée du Six-Août 13, 4000 Liège, Belgium.

\* Corresponding author: Prof. Rudi Cloots, [rcloots@uliege.be](mailto:rcloots@uliege.be)

## Abstract

Sb<sub>2</sub>S<sub>3</sub> stands out as low toxic, promising material for photovoltaic applications because of its unique optoelectronic properties such as a suitable band gap (1.4-1.8 eV), a high absorption coefficient (10<sup>5</sup> cm<sup>-1</sup>), appreciable thermal and chemical stability, and a high tolerance to defects.

In the first part of this study, Sb(Ac)<sub>3</sub> and SbCl<sub>3</sub> are compared as antimony precursor for the formation of the Sb<sub>2</sub>S<sub>3</sub> photoactive film. The Sb(Ac)<sub>3</sub>/thiourea (TU) precursor solution allows the formation of films with higher coverage and uniformity than films obtained from SbCl<sub>3</sub>/TU. In terms of PV efficiencies, Sb(Ac)<sub>3</sub>/TU and SbCl<sub>3</sub>/TU based layers respectively lead to 4.9 % and 4.8% efficiencies. Indeed, the band gap of the Sb<sub>2</sub>S<sub>3</sub> layer obtained from Sb(Ac)<sub>3</sub>/TU (1.75 eV) is less favorable than from SbCl<sub>3</sub>/TU (1.65 eV). In addition, the [hk1] crystalline orientation of Sb<sub>2</sub>S<sub>3</sub> is more favorable for efficient charge transfer in the devices and is more present in the SbCl<sub>3</sub>/TU films.

In the second part, the incorporation of a mesoporous TiO<sub>2</sub> network is considered to improve the transport of charge at the Sb<sub>2</sub>S<sub>3</sub>/TiO<sub>2</sub> electron transport layer interface and hence enhance the efficiency of the devices. However, the PV efficiencies are significantly lower in the case of the mesoporous architecture, which is mainly attributed to a [hk0] misorientation of the crystals in the mesoporous architecture leading to poor charge transfer.

By studying the impact of antimony precursor and the nature of the TiO<sub>2</sub> electron transport underlayer (dense or mesoporous) on the properties of the Sb<sub>2</sub>S<sub>3</sub> photoactive film, we highlight that a combination of three factors is crucial to boost device efficiencies: uniformity/coverage, adequate bandgap, and more importantly crystalline orientation.

**Keywords:** Chalcogenide, Sb<sub>2</sub>S<sub>3</sub>, crystalline orientation, antimony precursor, texture factor, device architecture, solar cells.



## 1. Introduction

View Article Online  
DOI: 10.1039/D4EL00036F

The development of alternatives to lead-based perovskites is essential to overcome the challenges associated with their stability and toxicity, and to guarantee the long-term success of solar photovoltaic technologies. Chalcogenides have been identified as promising candidates. [1]


A chalcogenide is composed of an element from the chalcogen family (oxygen, sulfur, selenium, tellurium, or polonium) and a Group III, IV, VI or transition metal element. [2] Among chalcogenide, scientists are particularly interested in antimony sulfide ( $\text{Sb}_2\text{S}_3$ ) because of their excellent optoelectronic properties and low toxicity.

Chalcogenides stand out as promising materials for photovoltaic applications because of their unique optoelectronic properties. In particular, antimony sulfide ( $\text{Sb}_2\text{S}_3$ ) has a suitable bandgap (1.4-1.8 eV), a high absorption coefficient ( $10^5 \text{ cm}^{-1}$ ), appreciable thermal and chemical stability, and a high tolerance to defects, allowing the manufacture of solar cells that are more robust and less sensitive to process variations. [3]

Stibine  $\text{Sb}_2\text{S}_3$  has a quasi-one-dimensional (Q1D) crystal structure constituted of  $(\text{Sb}_4\text{S}_6)_n$  ribbons. Each ribbon is made up of two triangular-based pyramids of  $\text{SbS}_3$  and two square-based pyramids of  $\text{SbS}_5$ . This anisotropic crystalline structure, unique to  $\text{Sb}_2\text{S}_3$ , induces anisotropic charge transport.[4] The performance of solar cells is therefore linked to the orientation of the ribbons, reported to be mainly  $[\text{hk}0]$ ,  $[\text{hk}1]$  and  $[\mathbf{001}]$  (**Figure 1**).[4] It has been found that charges are transported faster along orientation  $[\mathbf{001}]$ . Indeed, charge mobility and conductivity along this orientation are twice as high as those along the  $[\mathbf{010}]$  orientation and three times as high as those along the perpendicular  $[\mathbf{100}]$  orientation, as the vertical stacking along the  $[\mathbf{001}]$  direction favors 1D intra-ribbon transport.[4] On the contrary, films with a preferential  $[\text{hk}0]$  orientation, i.e. an orientation parallel to the substrate, do not exhibit satisfactory charges transport, as numerous recombination take place at the interface, due to inter-ribbon charge hopping mechanism.[5] This orientation is nevertheless the most widespread due to the low surface energy generated by the  $\text{Sb}_2\text{S}_3$  ribbons that grow along and spread over the substrate. The above growth process can mainly be related to the random crystal facets or low crystallization of  $\text{TiO}_2$  film, which cannot provide reliable epitaxial facets.[6] In addition, the crystal lattice mismatch at the interface between anatase  $\text{TiO}_2$  (electron transport layer, ETL) and  $\text{Sb}_2\text{S}_3$  disfavors a preferential  $[\mathbf{001}]$  orientation.[7] Furthermore, the large lattice mismatch with  $\text{TiO}_2$  can induce interface recombination due to the formation of dangling bonds at  $\text{Sb}_2\text{S}_3$  ribbon terminals.

In order to reduce recombination and improve charges transport, quasi-epitaxial growth with an  $[\text{hk}1]$  orientation, combining parallel  $[\text{hk}0]$  and vertical  $[\mathbf{001}]$   $\text{Sb}_2\text{S}_3/\text{TiO}_2$  interface, is thus a good compromise, guarantying efficient intra-ribbon carrier transport and reducing dandling bonds. As the very least, we therefore aim for a  $[\text{hk}1]$  orientation of the stibine coatings in our devices.



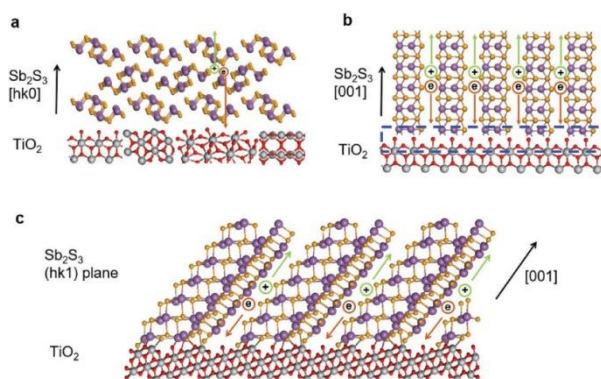

View Article Online  
DOI: 10.1039/D4EL00036F

Figure 1: (a) Crystal structures of  $(Sb_4S_6)_n$  ribbons stacked on  $TiO_2$  (a) in the  $[hk0]$  orientation, (b) in the  $[001]$  orientation and (c) in the  $[hk1]$  orientation. Reproduced with permission from [4]. Copyright 2024, John Wiley.

The orientation of  $Sb_2S_3$  can also be obtained by optimizing the heat treatment of  $TiO_2$  for lattice-matched tuning.[4] The microtopography of the  $TiO_2$  surface in the anatase phase differs according to the annealing temperature: smooth and uniform surface with small grain at low temperature and highly textured surface with very large, well-defined grains, which facilitated the latter heteroepitaxy, and potentially a phase transition to rutile at very high temperatures. Besides, thermal treatment can directly impact oxygen vacancy at the  $TiO_2$  surface.[6] Sb-S clusters with sulfur-rich dangling bonds could bind favorably with titanium atoms at  $TiO_2$  surface rich in oxygen vacancy. Higher annealing temperatures could introduce more oxygen vacancy and therefore sites that may favor latter  $Sb_2S_3$  bonding. To match the crystal lattices and bonding sites that facilitate  $[hk1]$  orientation of the  $Sb_2S_3$ , the  $TiO_2$  must be crystallized at a temperature of around  $550^\circ C$ .[7]

Studies of  $Sb_2S_3$  deposition have been carried out by rapid thermal evaporation [7], by vapor transport deposition and hydrothermal methods.[8,9] In this work, we focused on atmospheric pressure wet-deposition and more specifically spin-coating.

In addition, literature reports that the orientation of  $Sb_2S_3$  films depends on grain growth theory, influencing the way crystals form. [10] A progressive heat treatment promotes uniform growth with predominant  $[hk1]$  orientation. In contrast, rough annealing at high temperature produces large, flat grains, leading to anomalous growth where the  $[hk0]$  orientation predominates over  $[hk1]$ . These results highlight the importance of thermal control in modulating the properties of the  $Sb_2S_3$  films. Grains with an  $[hk0]$  orientation therefore grow faster than grains with an  $[hk1]$  orientation, leading to abnormal grain growth (**Figure 2**).

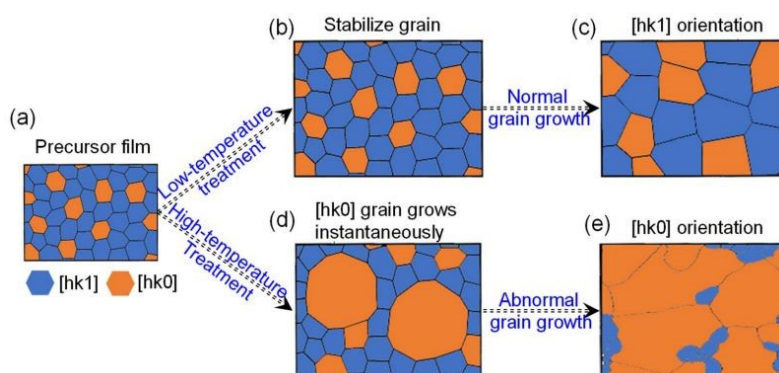


Figure 2: Mechanism of  $Sb_2S_3$  orientation dependence on grain growth. Surface texture of (a) the  $Sb_2S_3$  precursor film, (b) the  $Sb_2S_3$  precursor film after stabilization at low temperature, and (c) after normal grain growth. (d) and (e) represent the surface textures of the  $Sb_2S_3$  film after thermal treatment at high temperature and then subjected to abnormal grain growth. Reproduced with permission from [8] Copyright 2024, RSC.



Most studies use  $\text{SbCl}_3$ /thiourea precursors to form  $\text{Sb}_2\text{S}_3$  stibine. These studies notably focus on the ratio of  $\text{SbCl}_3$ /TU, S/Sb, concentrations, spin-coating speeds, etc (**Table 1**). However, efficient  $\text{Sb}_2\text{S}_3$  solar cells are mostly prepared by chemical bath deposition and hydrothermal methods, which require large amount of solution and can be time-consuming. These methods achieve PV efficiencies of around 7-8% for the best solar cells (**Table 1**).

Nevertheless, the devices prepared by spin-coating recently reached a new record of power conversion efficiency of 7.7% [11], which is comparable to the best photovoltaic performances achieved by chemical bath deposition or hydrothermal techniques. This improvement in PV efficiency involved the introduction of silver (Ag) ions into the  $\text{Sb}_2\text{S}_3$  sol-gel precursors, effectively influencing the crystallization and charge transport characteristics of  $\text{Sb}_2\text{S}_3$ . Consequently, the charge collection efficiency improved, and charge recombination losses decreased. However, in this work, we aim to focus on the pure  $\text{Sb}_2\text{S}_3$  formulation.

Table 1: Performances of spin-coated  $\text{Sb}_2\text{S}_3$  devices.[12]

	Studied experimental settings	Controlled property	Efficiency (%)	Ref.
$\text{SbCl}_3$ /thiourea	Spin-coating cycles	Crystallinity	2.3	[13]
	$\text{SbCl}_3$ :TU ratio	Grain size	4.4	[14]
	Annealing temperature	Surface roughness and grain size	4.3	[15]
	$\text{SbCl}_3$ :TU ratio	Grain growth and size	2.7	[16]
	$\text{SbCl}_3$ concentration	Uniformity	6.3	[17]
	Concentration of TU	Surface coverage	5.7	[18]
	Zn doping	Crystallinity	6.4	[19]
	Alkali metal doping	Crystallinity and grain size	6.6	[20]
	Pre-annealing process	Impurity phases	6.8	[21]
	Doping process	Surface uniformity	1.8	[22]
	Annealing temperature	Crystallinity	1.7	[23]
	Spinning speed	Pin holes	2.4	[24]
	Interfacial layer ( $\text{SbCl}_3$ )	Surface continuity	6.9	[25]
Ag doping	Crystallinity	7.7	[11]	
$\text{Sb}(\text{Ac})_3$ /thiourea	S/Sb ratio	Surface morphology	2.8	[25]
	$\text{Sb}_2\text{S}_3$ seed-mediated growth	Surface defects	5.1	[26]
	Concentration and S/Sb molar ratio	Film formation	5.7	[27]

Besides, a few groups use antimony acetate as a source of antimony, with convincing results in term of PV efficiency. [25-27] The best efficiency (5.7%) was obtained by Zhu *et al.* They grew  $\text{Sb}_2\text{S}_3$  films in situ on  $\text{TiO}_2$  nanoparticle films and investigated the effects of the concentration and S/Sb molar ratio in the precursor solution on the  $\text{Sb}_2\text{S}_3$  film formation and device performances. [28] Moreover, antimony acetate is generally considered to be less toxic than antimony chloride.



To the best of our knowledge, a comparative study of these two precursors has never been published yet. Comparing the structural and electronic properties of  $\text{Sb}_2\text{S}_3$  films obtained from both precursors can help at identifying and rationalizing differences in microstructure, crystallinity, grain size, texture, surface morphology and crystal orientations. So, in the first part of the article, we implement  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  precursors for the formation of  $\text{Sb}_2\text{S}_3$  films and compare their influence on the (micro)structural and optoelectronic properties of the films and their impact on the PV performances of the assembled devices.

In addition, in the second part of this work, we compare for the first time 2 types of device architectures: “dense” (only dense  $\text{TiO}_2$  as ETL) and “mesoporous” (addition of a mesoporous  $\text{TiO}_2$  layer between the dense  $\text{TiO}_2$  and the photoactive layer) architectures, to determine the effects of mesoporous  $\text{TiO}_2$  in  $\text{Sb}_2\text{S}_3$  devices.

All in all, this study highlights a combination of three key parameters for improving photovoltaic efficiency in  $\text{Sb}_2\text{S}_3$  solar cells: uniformity and coverage rate, adequate bandgap, and crystal orientation of the  $\text{Sb}_2\text{S}_3$  photoactive layer.

View Article Online  
DOI: 10.1039/D4EL00036F



## 2. Experimental section

View Article Online  
DOI: 10.1039/D4EL00036F

### 2.1. Materials and Chemical

Fluorine-doped tin oxide (FTO) covered glass of 2.2 mm thickness and 15  $\Omega$ /sq sheet resistance (TEC15, Greatcell Solar Materials) is used as substrates. The following chemicals are purchased from various commercial suppliers: hydrochloric acid HCl (VWR, 37%), metallic zinc powder (Roth,  $\geq 98\%$ ), titanium diisopropoxide bis(acetylacetonate) TAA (Sigma-Aldrich, 75 wt.% in isopropanol), anhydrous ethanol EtOH (Acros, 99.5%), TiO<sub>2</sub> nanoparticle paste 18NR-T (Greatcell Solar Materials), titanium chloride TiCl<sub>4</sub> (Merck,  $\geq 97.0\%$ ), antimony trichloride SbCl<sub>3</sub> (Sigma-Aldrich,  $> 99\%$ ), thiourea TU (Sigma-Aldrich,  $>99\%$ ), antimony triacetate Sb(Ac)<sub>3</sub> (Sigma-Aldrich,  $> 99.9\%$ ), N,N'-dimethylformamide DMF (Acros Organics, 99.9%), anhydrous chlorobenzene CB (Sigma-Aldrich, 99.8%), 2,2',7,7'-Tetrakis[N,N-di(4-methoxyphenyl)amino]-9,9'-spirobifluorene – Spiro-OMeTAD (Borun,  $>99.9\%$ ), lithium bis(trifluoromethanesulfonyl)imide Li-TFSI (Sigma-Aldrich, 99.95%), 4-tert-butylpyridine tBP (Sigma-Aldrich, 96%), anhydrous n-butanol n-BuOH (Fisher,  $>99.8\%$ ).

### 2.2. Substrate preparation

First, FTO glass substrates were cut into 2.0 x 2.0 cm<sup>2</sup> pieces then etched with HCl (2 M) and metallic zinc powder to strip parts of the FTO and prevent short circuits in the final PV cell. Substrates were cleaned over three consecutive washing steps (with soap, ethanol and acetone, respectively) under ultrasonication before being dried under air. A dense hole blocking layer of TiO<sub>2</sub> (c-TiO<sub>2</sub> ~30 nm thick) was then deposited by ultrasonic spray pyrolysis of TAA (2.2 mL) in ethanol (30.0 mL) from a Sono-Tek Exactacoat system combined with an Accumist nozzle. The following spraying parameters were used: stall power of 3.5 W, oxygen carrier gas flow of 0.9 psi, flow rate of 0.25 mL.min<sup>-1</sup>, nozzle speed of 100 mm.s<sup>-1</sup>, area spacing of 4 mm, nozzle-to-substrate distance of 5.5 cm, substrate temperature of 450°C. The deposition pattern was repeated 3 times to obtain a 30 nm thick TiO<sub>2</sub> film. Finally, a post-thermal treatment at 500°C (ramp 100°C/h) was performed for 30 min to crystallize TiO<sub>2</sub> in form of anatase phase. After a cleaning treatment under UV-ozone for 15 min, a 150 nm thick mesoporous (mp-)TiO<sub>2</sub> layer was deposited onto the c-TiO<sub>2</sub> layer. Commercial TiO<sub>2</sub> nanoparticle paste (18NR-T, Greatcell Solar Materials) was diluted in absolute ethanol (1:9.8 weight ratio) and spin-coated at 1500 rpm for 30 s, followed by subsequent annealing at 500 °C (with a ramp of 100°C/h) for 30 min. The mp-TiO<sub>2</sub> layer was immersed in an aqueous TiCl<sub>4</sub> solution (4.10<sup>-2</sup> M) for 30 min at 60°C to allow further improvement of the connectivity between the TiO<sub>2</sub> nanoparticles. Then, samples were successively rinsed with water and EtOH, dried with compressed air and then calcined for 30 min at 450°C in a preheated oven. Before the Sb<sub>2</sub>S<sub>3</sub> film deposition, a final cleaning treatment under UV-ozone for 15 minutes was applied to the samples.





### 2.3. Photoactive $\text{Sb}_2\text{S}_3$ film preparation

*Sb(Ac)<sub>3</sub>/TU precursors:* A 1 M solution of  $\text{Sb}_2\text{S}_3$  precursors was prepared outside the glovebox from  $\text{Sb(Ac)}_3$  and thiourea in a molar ratio of (1:1.8). 0.29889 g of  $\text{Sb(Ac)}_3$  was dissolved in 1 mL of DMF. Once the  $\text{Sb(Ac)}_3$  was completely dissolved, the thiourea was added ( $m = 0.13702$  g) and the mixture was stirred vigorously until the thiourea was completely dissolved. Note that the solution tends to precipitate after one hour.

*SbCl<sub>3</sub>/TU precursors:* A 1 M solution of  $\text{Sb}_2\text{S}_3$  precursors was prepared in a glovebox from  $\text{SbCl}_3$  and thiourea in the same molar ratio as above (1:1.8). 0.22812 g of  $\text{SbCl}_3$  was dissolved in 1 mL of DMF. Next, 0.13702 g of thiourea was added and the mixture was stirred vigorously for at least 40 min to allow complexation of the two compounds.

### 2.4. Photoactive $\text{Sb}_2\text{S}_3$ film deposition

The  $\text{Sb(Ac)}_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  solutions were deposited onto the FTO glass/c- $\text{TiO}_2$  substrates by spin-coating at 4200 RPM for 40 s in a glovebox. As mentioned in the introduction, a temperature gradient is necessary to promote the orientation [hk1] of the  $\text{Sb}_2\text{S}_3$  crystals. A heat treatment in several stages was therefore applied: 100°C (60 min) - 180°C (10 min) - 265°C (30 min) and enabled the optimum to be obtained in terms of film morphology (high coverage, and uniformity, smoothness). In addition, in order to further improve the film morphology features, a 1 M TU-DMSO post-treatment was carried out immediately after the last thermal step at 265°C (30 min). 0.07612 g of TU was added in 1 mL of DMSO. The post-treatment solution was also applied by spin-coating at 5000 RPM for 30 s, followed by a heat treatment at 300°C for 5 min.

The  $\text{SbCl}_3/\text{TU}$  was deposited onto the FTO glass/c- $\text{TiO}_2/\text{mp-TiO}_2$  substrates by spin-coating at 4200 RPM for 40 s in a glovebox. A multi-step thermal treatment was then applied: 150°C (10 min) – 265°C (30 min) – 300°C (10 min). No TU-DMSO post-treatment was applied, as this did not improve film properties.

### 2.5. Solar cell fabrication

First, Spiro-OMeTAD (186 mg) and an additive solution (84  $\mu\text{L}$ ) were mixed with anhydrous chlorobenzene (2 mL). The additive solution was prepared from 0.175 g Li-TFSI and 312.5  $\mu\text{L}$  of tert-butylpyridine in 1 mL of anhydrous butanol. The solution was then deposited by spin coating at 2000 RPM for 60 s.

After having scratched off the  $\text{TiO}_2/\text{Sb}_2\text{S}_3/\text{Spiro-OMeTAD}$  layers from the photoanode contact, a gold counter-electrode layer is deposited by thermal evaporation (home-made apparatus) using a patterned mask.

View Article Online  
DOI: 10.1039/D4EL00036F



## 2.6.Characterization

A field emission gun microscope TESCAN CLARA (FEI) under a 15-kV accelerating voltage and high vacuum was used for the morphological characterization of individual layers and assembled cells by scanning electron microscopy (SEM). All samples were coated with gold before characterization.

Optical profilometer images were recorded with an instrument Wyko NT9100 (X20, X50 objectives) with the measuring mode VSI-VXI, back scan = 10  $\mu\text{m}$ , length = 10  $\mu\text{m}$ .

X-ray diffraction (XRD) was conducted in the fixed  $\theta$ - $2\theta$  geometry on a Bruker D8 grazing incidence diffractometer instrument using a Cu K $\alpha$  source ( $\lambda = 1.5406 \text{ \AA}$ ) at a current of 40 A and voltage of 40 V. All references were taken from the PDF4+ database from the International Center for Diffraction Data.

A Shimadzu 3600 Plus instrument with an integrating sphere (ISR-1503) was used for optical measurements by UV-VIS-NIR spectrometry.

The depth profile of the films was investigated using a Thermofisher K-alpha X-ray photoelectron spectrometer (XPS), equipped with a monochromatic Al K $\alpha$  source and calibrated with the adventitious carbon (C1s) peak. An Ar ion gun was used to progressively strip (0.3 nm/s) and then probe the elements as they were removed.

A class A solar simulator (Newport Spectra Physics) coupled to a Keithley 2400 sourcemeter measures the PV conversion efficiency of the cells. Calibration was performed using a KG5 filtered silicon reference solar cell from Newport. Photocurrent density versus applied voltage curves (J-V curves) were measured on 2.0 x 2.0 cm<sup>2</sup> devices under simulated 1 SUN illumination (filter AM 1.5) at room temperature, using a black mask with a 0.0355 cm<sup>2</sup> aperture. Forward (0V to 1.2 V) and backward (1.2 V to 0V) measurements were performed with an increment of 4 mV (0.2s/step).

For the electrochemical impedance spectroscopy (EIS), data were collected using a BioLogic SP-200 potentiostat (Science Instrument) and analyzed with the EC-Lab software. A sinusoidal potential perturbation was applied on the assembled devices and the current variation response was recorded. A frequency range of 3 MHz to 85 mHz with 10 mV sinusoidal modulation was applied for the EIS data acquisition. Measurements were performed at room temperature under standard 1 SUN illumination (AM 1.5 filter) and in open circuit potential (OCP) conditions.




### 3. Results and discussion

#### 3.1. Choice of the antimony precursor for the formation of $\text{Sb}_2\text{S}_3$

View Article Online  
DOI: 10.1039/D4EL00036F

##### 3.1.1. Structure and morphology of $\text{Sb}_2\text{S}_3$ thin films

First, the morphology of the  $\text{Sb}_2\text{S}_3$  films was evaluated by scanning electron microscopy (SEM) analysis (**Figure 3 a-d**).  $\text{Sb}(\text{Ac})_3/\text{TU}$  precursor solution allows the formation of a very smooth and uniform chalcogenide film whereas  $\text{SbCl}_3/\text{TU}$ -based films are less covering and less uniform. The distinct morphologies of  $\text{Sb}(\text{Ac})_3$  and  $\text{SbCl}_3$  films may stem from their differing chemical properties. The acetate groups in  $\text{Sb}(\text{Ac})_3$  seem to provide molecular deformability, which could promote more homogeneous solvation and uniform nucleation during thin film formation. In contrast,  $\text{SbCl}_3$  exhibits more heterogeneous interactions. [29] This difference may account for the smoother film obtained with  $\text{Sb}(\text{Ac})_3$ . Further investigations, including theoretical studies, will be necessary to validate these proposed molecular mechanisms. Optical profilometer measurements (**Figure 3 e-f**) corroborate the higher uniformity of  $\text{Sb}(\text{Ac})_3/\text{TU}$  film with a lower  $R_q$  ( $R_q=1.19$  nm) than for  $\text{SbCl}_3/\text{TU}$  film ( $R_q=2.01$  nm). For both films, the thickness is similar ( $\sim 110$  nm). As the charge diffusion length of stibine is between 30 and 300 nm, a layer thicker than 300 nm could lead to increased recombination and reduce the efficiency of the solar cell. [30]

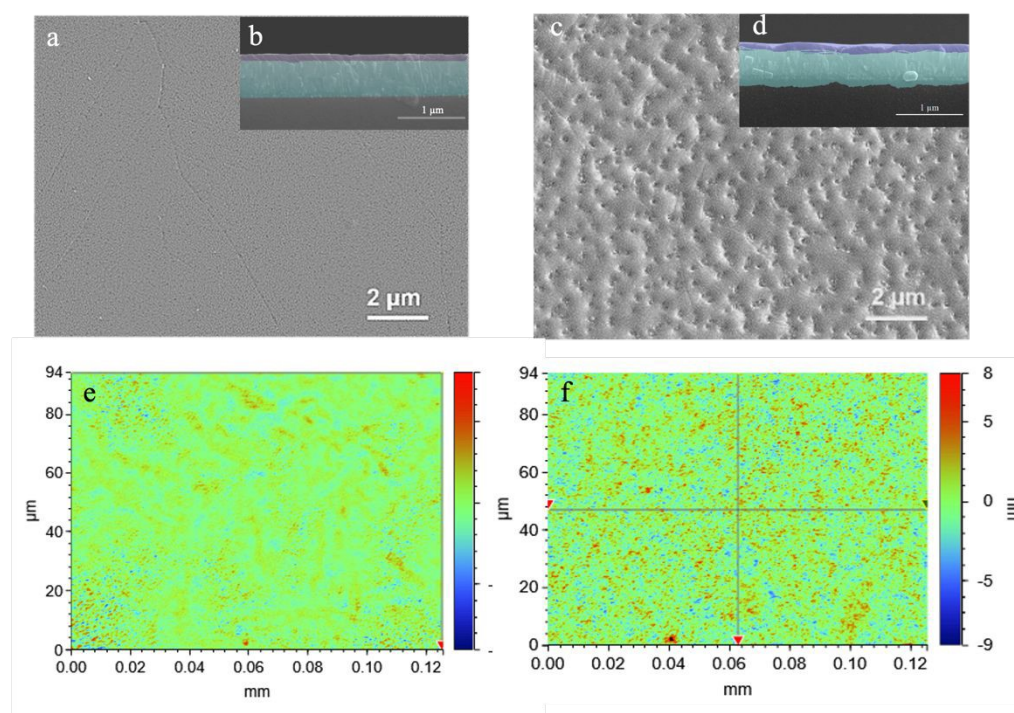

*Figure 3: SEM micrographs in top-view and cross-section (inset) of (a-b)  $\text{Sb}(\text{Ac})_3/\text{TU}$  and (c-d)  $\text{SbCl}_3/\text{TU}$  films. The following color code is used to label the consecutive layers: FTO glass (turquoise) and  $\text{Sb}_2\text{S}_3$  (purple). Optical profilometer images of (e)  $\text{Sb}(\text{Ac})_3/\text{TU}$  and (f)  $\text{SbCl}_3/\text{TU}$  films.*

X-ray diffraction (XRD) measurements were performed on the  $\text{Sb}_2\text{S}_3$  layers obtained from  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  solutions. **Figure 4** shows the XRD patterns of the stibine  $\text{Sb}_2\text{S}_3$ . We can observe that the  $\text{Sb}_2\text{S}_3$  films formed from  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  are both crystallized.  $\text{Sb}_2\text{S}_3$  average crystallite size was calculated from Scherrer equation on the most



intense peak signals. No significant difference is observed between  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  samples, with  $30 \pm 4$  nm and  $28 \pm 3$  nm average values respectively extracted. As charge transport is anisotropic in  $\text{Sb}_2\text{S}_3$ , solar cell performance should be linked to the crystalline orientation of the material. It was found that the most experimentally feasible orientation in  $\text{Sb}_2\text{S}_3$  samples that allows rapid charge transport is the  $[\text{hk}1]$  orientation. [5], [7]

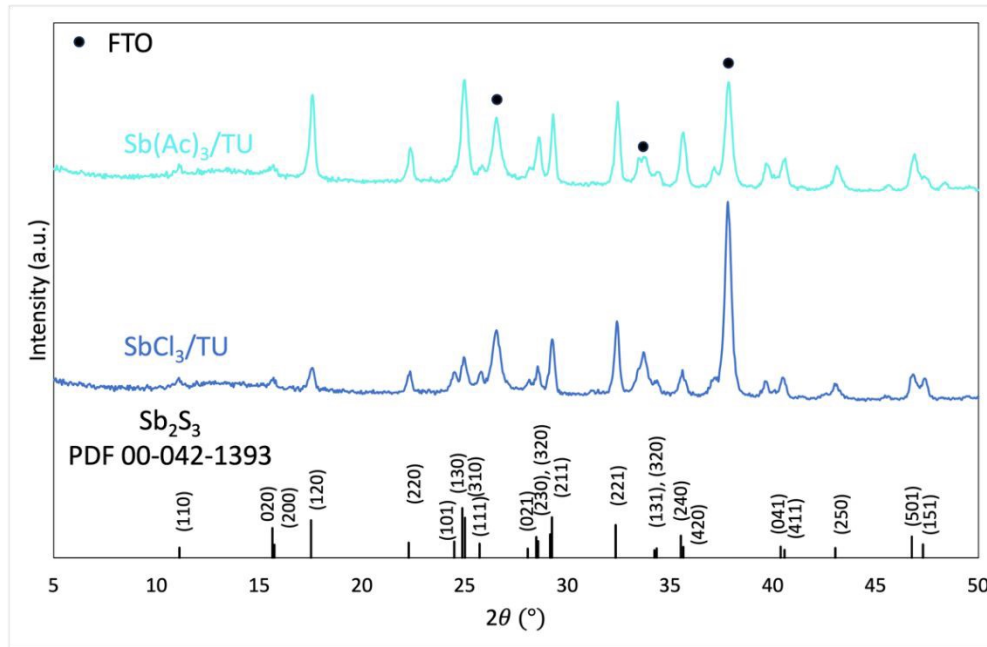


Figure 4 : X-ray diffractograms of  $\text{Sb}_2\text{S}_3$  films from  $\text{Sb}(\text{Ac})_3/\text{TU}$  (turquoise) (a) and  $\text{SbCl}_3/\text{TU}$  (dark blue) (b) solutions.

The relative intensities and texture coefficients (**Figure 5a**) were calculated to compare the preferred orientation of the films. From the relative intensities (**Equation 1.**), films formed from  $\text{Sb}(\text{Ac})_3/\text{TU}$  have more intense peaks in the  $(120) > (130) > (221) > (211) > (420)$  planes whereas the films formed from the  $\text{SbCl}_3/\text{TU}$  precursor solution have more intense peaks for the  $(221) > (211)$  planes. The  $[\text{hk}1]$  orientation, necessary for improved charge transport, seems then to be more present for the  $\text{SbCl}_3/\text{TU}$  precursor.

$$\text{Relative intensity} = \frac{I(hkl)}{\sum_{i=1}^N I(hkl)} \quad (3.1.)$$

where  $I(hkl)$  is the intensity of the diffraction peak of the  $hkl$  plane obtained in the measured diffractogram.

To probe the preferential orientation in the  $\text{Sb}_2\text{S}_3$  films, the texture factor (TC) was used to normalize the experimental intensities based on simulated  $\text{Sb}_2\text{S}_3$  intensities in the same conditions of measurements. TC was calculated from **Equation (2.)** [31]:

$$TC(hkl) = \frac{\frac{I(hkl)}{I_0(hkl)}}{\left[ \frac{1}{N} \sum_{i=1}^N \frac{I(hkl)}{I_0(hkl)} \right]} \quad (3.2.)$$

where:

$I(hkl)$  is the intensity of the diffraction peak of the  $hkl$  plane obtained in the measured diffractogram;



$I_0(hkl)$  is the theoretical/simulated intensity of the diffraction peak obtained from PDF 00-042-1393 for the given  $hkl$  plane; [32] [18], [28], [33], [34], [35]

View Article Online  
DOI: 10.1039/D4EL00036F

$N$  is the number of  $hkl$  planes considered.

By convention, TC values greater than 1 reflect a preferential orientation of the considered crystalline planes.

To improve the data analysis accuracy, deconvolution was carried out when necessary, using Bruker software (DIFFRAC.TOPAS). The texture factor was calculated on peaks between 5-50°. Only a few peaks with very low intensity were neglected to minimize the error on the calculated values. A comparison of the texture coefficients (**Figure 5b**) for the two precursors shows that the (041) > (411) > (311) > (221) > (420) > (220) planes present a preferential orientation with TC values greater than 1 for samples obtained from  $SbCl_3/TU$ , whereas for samples obtained from  $Sb(Ac)_3/TU$ , the (130) > (420) > (411) > (230) > (041) > (220) planes are preferred. Then, the  $[hk1]$  crystalline orientation of stibine is predominant for the  $SbCl_3/TU$  films whereas  $[hk0]$  planes are more present for  $Sb(Ac)_3/TU$  films.

A recent study showed that the  $TiO_2$  crystallization at 500°C favors the matching of the crystal networks and bonding sites between the  $TiO_2$  and the  $Sb_2S_3$ , facilitating  $[hk1]$  oriented growth.[10] In addition, the  $Sb_2S_3$  samples studied here were annealed from a low temperature (100°C) to a higher temperature (265°C). This stabilization process should allow normal grain growth, favoring the presence of the  $[hk1]$  orientation (**Figure 2**). The difference in crystalline orientation should therefore come here only from the precursors used as the thermal treatments for  $TiO_2$  and  $Sb_2S_3$  are the same. Preferential orientation induced by the precursor nature has never been reported to date in the literature to the best of our knowledge and could help to explain the differences in PV efficiency measured in full devices. From this point of view,  $SbCl_3/TU$  precursors give the best results.





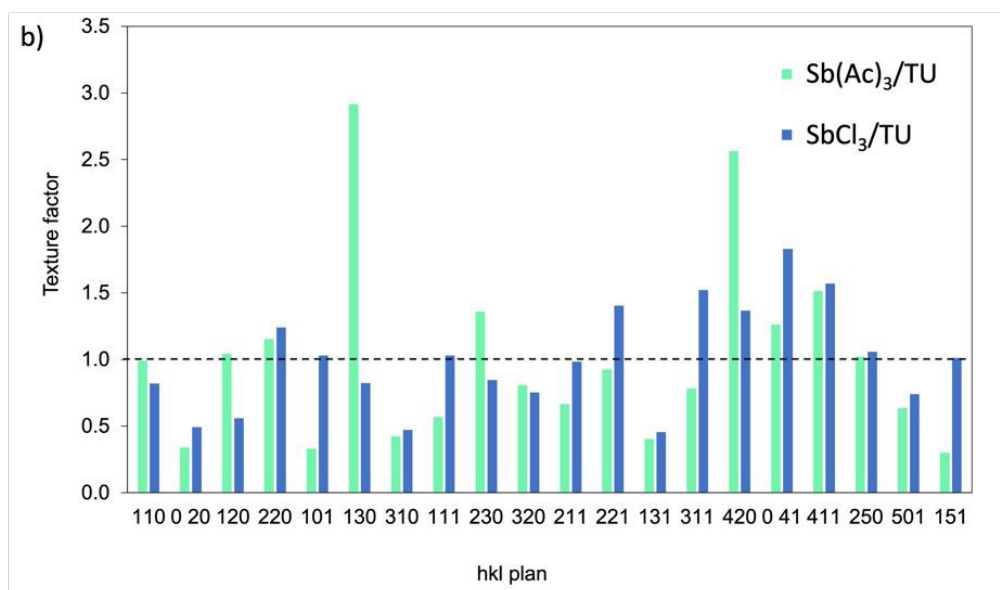


Figure 5: (a) Relative intensity and (b) texture coefficient for different (hkl) planes of  $Sb_2S_3$  films from  $Sb(Ac)_3/TU$  and  $SbCl_3/TU$  precursor solutions.

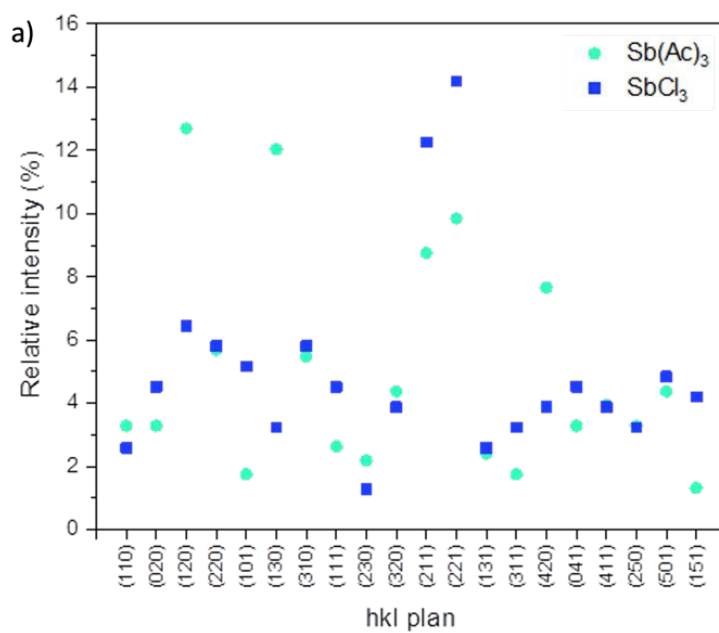

### 3.1.2. Optical properties of $\text{Sb}_2\text{S}_3$ thin films

View Article Online  
DOI: 10.1039/D4EL00036F

The optical absorbance spectra of  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  thin films are reported in **Figure 6**. The absorbance is globally equivalent for both films in the range of solar spectrum radiation.  $\text{Sb}(\text{Ac})_3/\text{TU}$  films absorb more below  $\sim 570$  nm but less above  $\sim 570$  nm than  $\text{SbCl}_3/\text{TU}$  films. Tauc plots allow the determination of a direct bandgap of  $\sim 1.65$  and  $\sim 1.75$  eV respectively for  $\text{SbCl}_3/\text{TU}$  and  $\text{Sb}(\text{Ac})_3/\text{TU}$  samples, which are in accordance with the ones previously reported in the literature for similar synthesis conditions. [4],[5] Reducing the bandgap from 1.75 eV to 1.65 eV can improve photovoltaic efficiency by broadening the absorption spectrum, enabling the material to absorb more photons, particularly in the visible range. The result is a higher short-circuit current density ( $J_{\text{sc}}$ ). The optimized bandgap strikes an ideal balance between open-circuit voltage ( $V_{\text{oc}}$ ) and  $J_{\text{sc}}$ , improving both without sacrificing either. Additionally, the narrower bandgap improves charge collection efficiency by reducing recombination losses and enhancing charge transport, as energy alignment at the interfaces is more favorable for carrier extraction, increasing overall device performance.

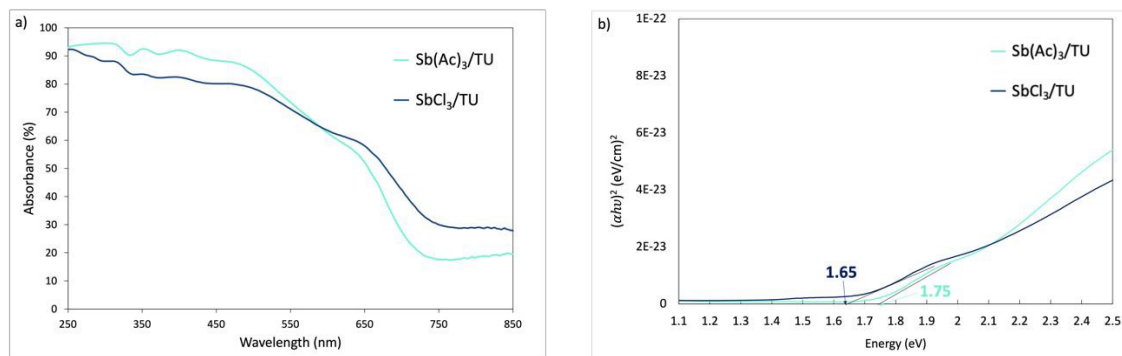


Figure 6. (a) Absorbance spectra of  $\text{Sb}_2\text{S}_3$  films from  $\text{Sb}(\text{Ac})_3/\text{TU}$  (turquoise) and  $\text{SbCl}_3/\text{TU}$  (dark blue) precursor solutions. (b) Tauc plots of  $\text{Sb}_2\text{S}_3$  films from  $\text{Sb}(\text{Ac})_3/\text{TU}$  (turquoise) and  $\text{SbCl}_3/\text{TU}$  (dark blue) precursor solutions.

### 3.1.3. Assembly and characterization of $\text{Sb}_2\text{S}_3$ double perovskite solar cells

The PV performances of  $\text{Sb}_2\text{S}_3$  films prepared from  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$  were evaluated in devices assembled with the following architecture: glass/FTO/c-TiO<sub>2</sub>/ $\text{Sb}_2\text{S}_3$ /Spiro-OMeTAD/Au. The PCEs reported in this work (**Table 2** and **Table 3**) are similar for both precursor solutions, *i.e.*  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$ , and are in the upper range of efficiencies published to date (between 2.3% and 6.9%; **Table 1**) for spin-coated  $\text{Sb}_2\text{S}_3$  as photoactive material.[13], [15-17], [19-24], [32] The  $\text{Sb}(\text{Ac})_3/\text{TU}$  device tends to show slightly enhanced  $V_{\text{oc}}$  of 0.567 V (average:  $0.560 \pm 0.010\text{V}$ ) vs. 0.551 V (average:  $0.523 \pm 0.19\text{V}$ ) for  $\text{SbCl}_3/\text{TU}$  device. Indeed, the more uniform and covering  $\text{Sb}(\text{Ac})_3/\text{TU}$  film can lead to lowered recombination in devices. Fewer electrons are trapped in the intermediate energy levels, which further results in an increased open circuit potential. The  $J_{\text{sc}}$  values are little higher for  $\text{SbCl}_3/\text{TU}$  devices in comparison with  $\text{Sb}(\text{Ac})_3/\text{TU}$  corresponding to a slightly more efficient charge transfer into the selective contact. This difference in  $J_{\text{sc}}$  values could be due to a better [hk1] orientation and so a better charge transport within the layers, leading to improved charge collection at the electron selective contact and thus increased  $J_{\text{sc}}$ .



Table 2: Photovoltaic parameters of the best  $Sb_2S_3$ -based solar cellsView Article Online  
DOI: 10.1039/D4EL00036F

Solution	Direct				Reverse			
	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)
SbCl <sub>3</sub> - TU	0.531	16.2	43	3.7	0.551	17.5	50	4.8
Sb(Ac) <sub>3</sub> - TU	0.539	16.1	43	3.8	0.567	17.1	49	4.9

Table 3: Photovoltaic parameters of the  $Sb_2S_3$ -based solar cells (20 devices average)


Solution		Direct				Reverse			
		Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)
SbCl <sub>3</sub> - TU	<M>	0.487	16.1	44	3.5	0.523	15.8	49	4.1
	$\sigma$	0.020	1.2	2	0.4	0.019	1.1	2	0.5
Sb(Ac) <sub>3</sub> - TU	<M>	0.533	15.1	41	3.5	0.560	16.7	46	4.4
	$\sigma$	0.010	1.0	1	0.3	0.010	0.7	2	0.4

To further analyze the charge transfer properties of the  $Sb(Ac)_3/TU$  and  $SbCl_3/TU$ -based solar cells, EIS analyses were conducted, with results presented as Nyquist plots in **Figure 7**. Data were fitted with the equivalent circuit model shown in the inset and are summarized in **Table 4**. [36-38]

The equivalent electrical circuit consists in a resistance  $R_1$  (at high frequency), corresponding to the distance between the point (0,0) and the intersection of the first semicircle with the x-axis, which represents the series resistance ( $R_s$ ). This resistance is associated with wires and contacts. The second elements  $R_2 // Q_2$  are described by the first semicircle, at medium frequency-. They give information about the charge transfer at the interfaces between  $Sb_2S_3/HTL$  and/or  $TiO_2/Sb_2S_3$ .  $R_3 // Q_3$  elements at low frequency are related to electron-hole interfacial recombination.





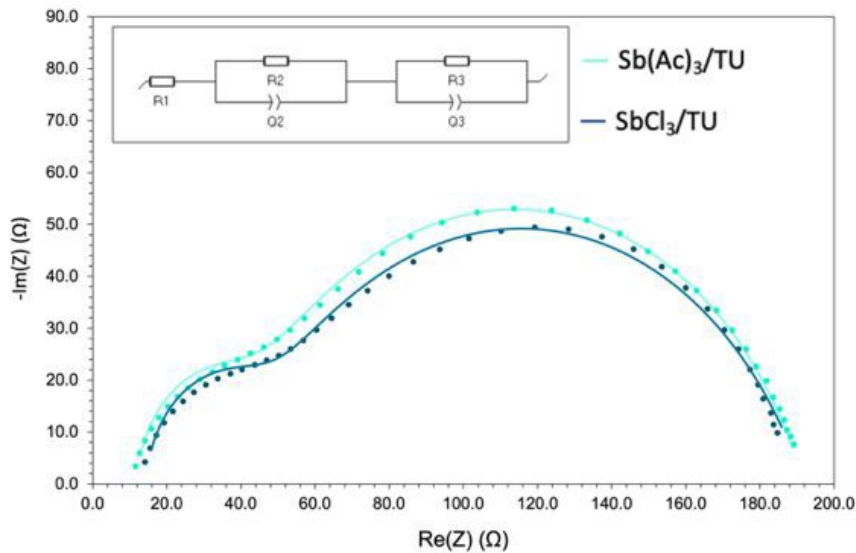

View Article Online  
DOI: 10.1039/D4EL00036F

Figure 7: EIS Nyquist plots of  $\text{Sb}(\text{Ac})_3/\text{TU}$  (turquoise) and  $\text{SbCl}_3/\text{TU}$  (dark blue)  $\text{Sb}_2\text{S}_3$ -based solar cells; inset: equivalent electrical circuit used for data fitting.

Table 4: Fitting resistance ( $R$ ) and constant phase element ( $Q$ ) parameters obtained from EIS data measured of  $\text{Sb}(\text{Ac})_3/\text{TU}$  and  $\text{SbCl}_3/\text{TU}$   $\text{Sb}_2\text{S}_3$ -based solar cells

	PCE (%)	$R_1$ [ $\Omega$ ]	$Q_2$ [ $10^{-3}$ F. $\text{s}^{a-1}$ ]	$a$	$R_2$ [ $\Omega$ ]	$Q_3$ [ $10^{-6}$ F. $\text{s}^{b-1}$ ]	$b$	$R_3$ [ $\Omega$ ]
$\text{Sb}(\text{Ac})_3\text{-TU}$	4.9 %	15	8.64	1	32	1.415	0.746	169
$\text{SbCl}_3\text{-TU}$	4.8 %	14	11.51	1	28	2.075	0.732	150

From data fitting (**Table 4**), the interfacial recombination resistance  $R_3$  of the  $\text{Sb}(\text{Ac})_3/\text{TU}$  device is 169  $\Omega$ , which is higher than  $R_3$  value of the  $\text{SbCl}_3/\text{TU}$  device (150  $\Omega$ ). As the recombination rate is inversely proportional to  $R_3$ , it reveals lower interfacial recombination in  $\text{Sb}(\text{Ac})_3/\text{TU}$  device. This should be more likely due to the more uniform film for  $\text{Sb}(\text{Ac})_3/\text{TU}$  precursors. Furthermore, the  $Q_3$  value is higher for  $\text{SbCl}_3/\text{TU}$  device which means a higher accumulation of charge at the interface, less favorable for PV devices. This is in agreement with the  $V_{oc}$  values obtained for the devices, as higher interfacial recombination and charge accumulation at the interface increase the forward bias diffusion current, which in turn reduces the open-circuit voltage. [39]

Looking at  $R_2$  charge transfer to the selective contacts resistance, we determined a slightly lower  $R_2$  value for  $\text{SbCl}_3/\text{TU}$  (28  $\Omega$ ) compared to the  $\text{Sb}(\text{Ac})_3/\text{TU}$  (32  $\Omega$ ) device, corresponding to a slightly more efficient charge transfer into the selective contact for the  $\text{SbCl}_3/\text{TU}$  device and so a higher  $J_{sc}$  value. This difference in  $J_{sc}$  values could be due to a better [hk1] orientation and so a better charge transport within the layers, leading to improved charge collection at the electron selective contact and thus increased  $J_{sc}$ . The EIS data thus globally corroborate J-V results.

This study shows that the  $\text{Sb}(\text{Ac})_3/\text{TU}$  precursor solution produces films with better coverage and uniformity than films obtained from the  $\text{SbCl}_3/\text{TU}$  precursor solution. We would therefore expect to obtain better PV efficiencies for devices assembled from these films compared with  $\text{SbCl}_3/\text{TU}$ . However, the bandgap value (1.75 eV) is less favorable than for  $\text{SbCl}_3/\text{TU}$  (1.65



eV). In addition, the crystalline orientation [hk0] is more present in Sb(Ac)<sub>3</sub>/TU films, which does not favor efficient charge transfer in the devices. The preferential [hk0] orientation parallel to the Sb<sub>2</sub>S<sub>3</sub>/TiO<sub>2</sub> interface - of Sb(Ac)<sub>3</sub>/TU films could probably explain their better uniformity and coverage. Further study of the heat treatment and Sb:S ratio for films obtained with Sb(Ac)<sub>3</sub>/TU precursors could be beneficial to improve efficiencies through fine tuning of band gap and [hk1] crystalline orientation. All in all, a combination of three key factors can be highlighted to increase the efficiency of the assembled devices : uniformity and coverage of the photoactive layer, adequate bandgap and preferred [hk1] crystalline orientation.

View Article Online  
DOI:10.1039/D4EL00036F



### 3.2. Effect of the cell architecture in $\text{Sb}_2\text{S}_3$ devices

View Article Online  
DOI: 10.1039/D4EL00036F

#### 3.2.1. Structure and morphology of $\text{Sb}_2\text{S}_3$ thin film

In the first part of this study, tests were carried out with a dense layer of  $\text{TiO}_2$  as ETL (**Figure 8a**). Alternatively, a stibine-infiltrated mesoporous  $\text{TiO}_2$  layer can be incorporated on top of the dense  $\text{TiO}_2$  layer in the device stack (**Figure 8b**). This architecture is envisaged to increase the quantity of photoactive material while keeping efficient charge diffusion and separation in the devices thanks to ETL/ $\text{Sb}_2\text{S}_3$  interpenetration, and thus boost PV efficiencies. The two following device architectures (**Figure 8**) with  $\text{SbCl}_3/\text{TU}$  as stibine precursors are then compared: glass/FTO/c- $\text{TiO}_2/\text{Sb}_2\text{S}_3/\text{Spiro-OMeTAD}/\text{Au}$  (referred as “dense” architecture) vs. glass/FTO/c- $\text{TiO}_2/\text{mp-TiO}_2/\text{Sb}_2\text{S}_3/\text{Spiro-OMeTAD}/\text{Au}$  (referred as “mesoporous” architecture).

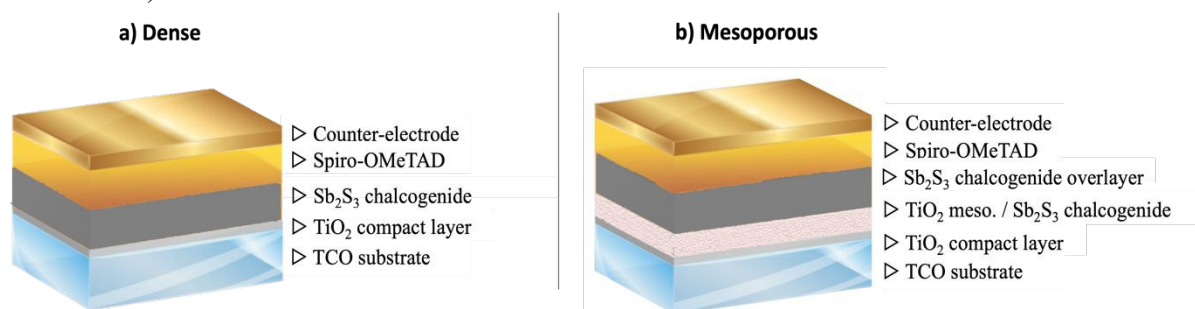


Figure 8: Scheme of dense and mesoporous architectures of  $\text{Sb}_2\text{S}_3$  devices.

SEM micrographs show that the substrate is not completely covered with stibine and is less covering in mesoporous architecture than in dense one. Small clusters appear to be deposited onto the mesoporous  $\text{TiO}_2$  surface, which is visible below. From the cross-section micrographs, it is not possible to see if the stibine is infiltrated into the mesoporous  $\text{TiO}_2$  network (**Figure 9**). The aim of mesoporous  $\text{TiO}_2$  is to increase the interaction interface with the stibine, thereby increasing charge separation and promoting electron collection and transport into the  $\text{TiO}_2$  network, ultimately increasing cell efficiency.

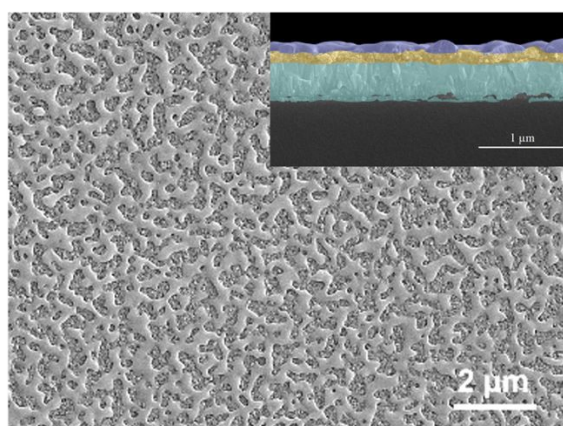


Figure 9: SEM micrographs in top-view and cross-section (inset) of glass/FTO/c- $\text{TiO}_2/\text{mp-TiO}_2/\text{Sb}_2\text{S}_3$  sample. The following color code is used to label the consecutive layers: FTO glass (turquoise), c- $\text{TiO}_2$  and mp- $\text{TiO}_2$  (yellow) infiltrated by  $\text{Sb}_2\text{S}_3$ , overlayer of  $\text{Sb}_2\text{S}_3$  (purple).



To verify the infiltration of  $\text{Sb}_2\text{S}_3$  into the mp- $\text{TiO}_2$ , an XPS profile analysis was carried out (Figure 10). The XPS profiles obtained for the glass/FTO/c- $\text{TiO}_2$ / $\text{Sb}_2\text{S}_3$  sample (Figure 10a) are presented and used as a reference to confirm the trends obtained for the XPS carried out on the glass/FTO/c- $\text{TiO}_2$ /mp- $\text{TiO}_2$ / $\text{Sb}_2\text{S}_3$  sample (Figure 10b).

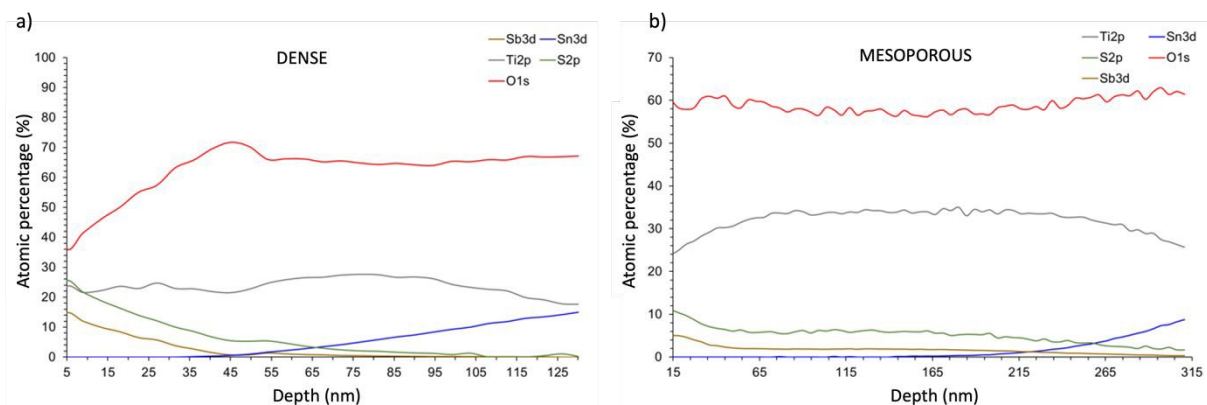


Figure 10: XPS profiles for sample a) glass-FTO/c- $\text{TiO}_2$ / $\text{Sb}_2\text{S}_3$  b) glass-FTO/c- $\text{TiO}_2$ /mp- $\text{TiO}_2$ / $\text{Sb}_2\text{S}_3$ .

On the “dense” sample (only c- $\text{TiO}_2$ ) XPS profile (Figure 10a), the initial atomic percentages of sulfur and antimony are 26 and 15% respectively. Titanium is also present at an atomic percentage of 24% because the stibine film does not completely cover the surface of the glass/FTO/c- $\text{TiO}_2$  substrate. As the analysis depth increases, the atomic percentages of sulfur and antimony decrease, reaching zero at around 115 nm, as expected from the film thickness observed by SEM. However, the tin characteristic of FTO glass appears at values of 50 nm. As the substrate is not completely covered by the stibine, it is possible for the ion beam to reach the FTO glass faster.

On the “mesoporous” sample (c- $\text{TiO}_2$  and mp- $\text{TiO}_2$ ) XPS profile (Figure 10b), an atomic percentage of 5% antimony and 11% sulfur was determined. This percentage corresponds to the stibine above the mesoporous  $\text{TiO}_2$  layer. A titanium percentage of around 23% was also determined. As observed on the SEM micrographs, the stibine layer does not completely cover the substrate, making the mp- $\text{TiO}_2$  “visible”. Between 15 and 55 nm depth, a slight decrease in atomic percentage is observed for antimony and sulfur, while the atomic percentage of titanium increases. This observation corresponds to interactions of the electron beam at the mp- $\text{TiO}_2$  / $\text{Sb}_2\text{S}_3$  interface. Between 55 and 175 nm, the atomic percentage of the various elements remains constant, indicating the presence of both  $\text{TiO}_2$  and  $\text{Sb}_2\text{S}_3$ . Finally, after 175 nm, the atomic percentage of sulfur and antimony decreases slightly, while that of  $\text{TiO}_2$  remains constant, corresponding to the arrival of the beam on the dense  $\text{TiO}_2$  layer. Next, the tin signal, which was zero until then, appears, indicating that the beam reaches the FTO glass substrate. The XPS profile therefore corroborates the infiltration of  $\text{Sb}_2\text{S}_3$  into mp- $\text{TiO}_2$ .

The diffractograms for both architectures (dense and mesoporous) were then compared (Figure 11) and we can observe that  $\text{Sb}_2\text{S}_3$  films are crystallized in both cases.



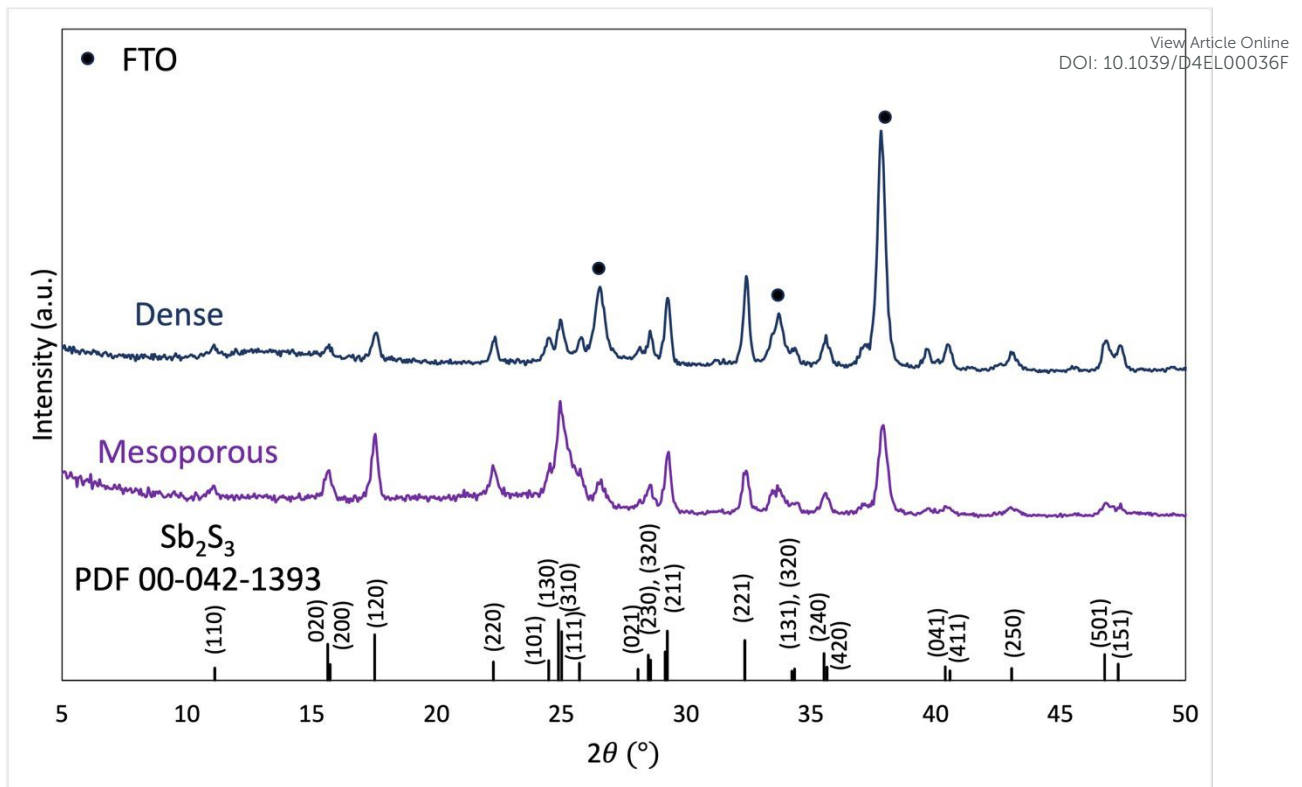


Figure 11: X-ray diffractograms of glass-FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (dark blue) and glass-FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (purple) samples.

Calculation of the relative intensities (**Figure 12a**, **Equation 1.**) highlights the planes with the highest intensity. For the mesoporous architecture, it turns out that the peaks relating to the (310) and (120) planes have the highest intensity, followed by the (211), (220) and (221) planes, whereas for the dense architecture, the (221) and (211) planes, followed by the (120) and (310) planes, are predominant. The texture factor TC (**Equation 2.**) was also calculated for both samples. The comparison of the texture coefficients (**Figure 12b**) for the two architectures shows that the (041) > (411) > (311) > (221) > (220) planes have TC greater than 1 for “dense” devices, whereas for “mesoporous” devices, the (220) > (110) > (310) > (120) > (130) > (420) > (230) planes show preferred orientation. It therefore appears that glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> films have a preferential [hk0] orientation, whereas glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> films have a preferential [hk1] orientation, the latter showing improved charge transport. This misorientation in mesoporous device could be caused by the confinement of the Sb<sub>2</sub>S<sub>3</sub> crystals within the mesoporous TiO<sub>2</sub> network. Indeed, in some studies, [38]-[40] they used larger pores (50-60 nm VS 25 nm for our study), and their PV efficiencies were higher. (from 5.1% to 7.5% vs. 2.3% for our devices). However, in these studies, the orientation of the crystals was not verified, which underlines the interest of our upstream work. Moreover, larger pores allow the growth of larger TiO<sub>2</sub> crystallites in the walls of the porous network, which has been reported to be critical for promoting [hk1] quasi-epitaxial growth at the Sb<sub>2</sub>S<sub>3</sub>/TiO<sub>2</sub> interface. In the mesoporous TiO<sub>2</sub> layer implemented in this paper, the crystallite size is around 15 nm and can reach 30-40 nm in a larger pore network, as we have already observed in other research developed at GREENMat aiming at the synthesis of opal-like porous TiO<sub>2</sub> network by hard templating, using polystyrene beads as sacrificial structuring agent.[37] This could explain the difference in results observed with [40]-[42].



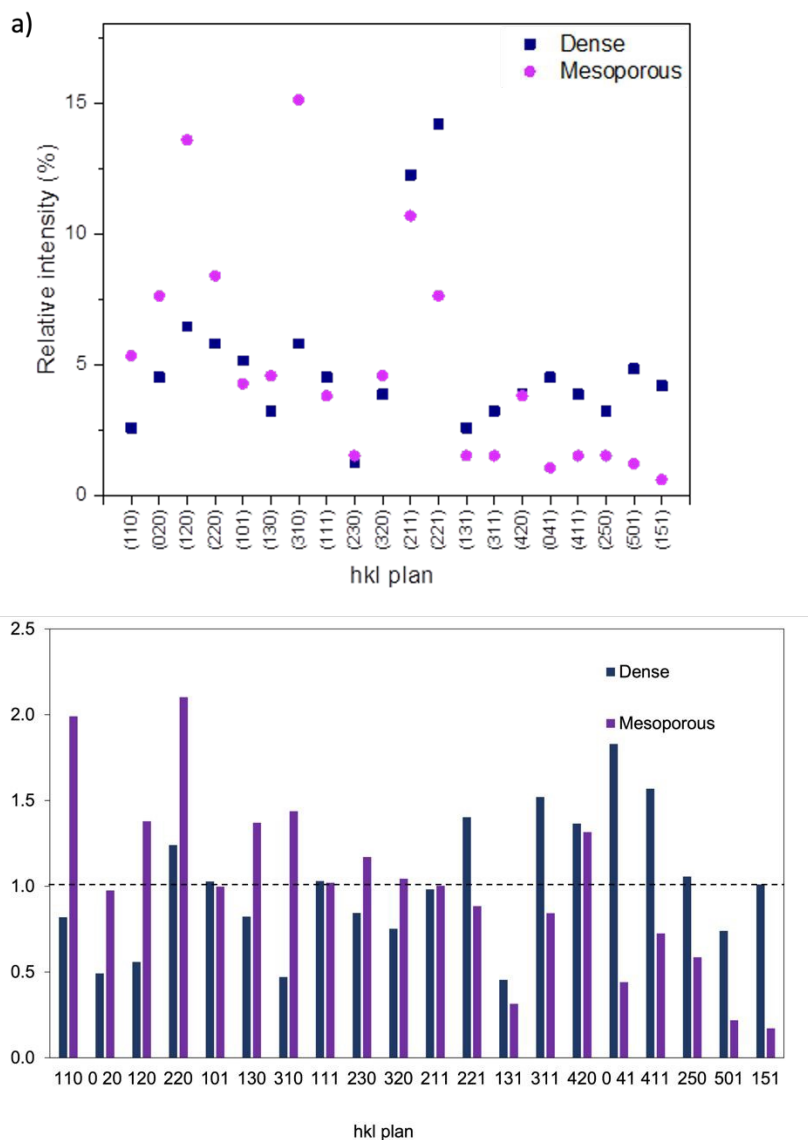


Figure 12: (a) Relative intensity and (b) texture coefficient for different (hkl) planes of glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (dark blue) and glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (purple) samples.



### 3.2.2. Optical properties of $\text{Sb}_2\text{S}_3$ thin films

View Article Online  
DOI: 10.1039/D4EL00036F

The optical absorbance spectra of glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> and glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> samples are reported in **Figure 13**. The absorbance is globally higher in the mesoporous architecture. This is due to the higher quantity of stibine material, *i.e.* infiltrated into the mesoporous TiO<sub>2</sub> and in the overlayer at the surface of the TiO<sub>2</sub> mesoporous network. Tauc plots allow the determination of a direct bandgap of  $\sim 1.65$  eV for both architectures. These values are in accordance with the ones previously reported in the literature for similar synthesis conditions.[4], [30] Furthermore, it is obvious that the values are similar because the precursors and the deposition method are identical for both architectures. Only the heat treatment slightly varies from one architecture to the other.

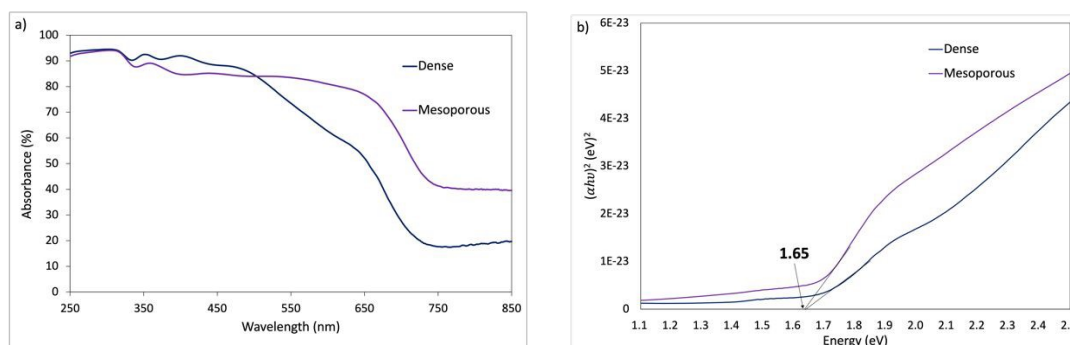


Figure 13: a) Absorbance spectra and (b) Tauc plots of glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (dark blue) and glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> (purple) samples.

### 3.2.3. Assembly and characterization of $\text{Sb}_2\text{S}_3$ double perovskite solar cells

The PV performances of the  $\text{Sb}_2\text{S}_3$  solar cells were evaluated for the following architectures: glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub>/Spiro-OMeTAD/Au (dense architecture) and glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub>/Spiro-OMeTAD/Au (mesoporous architecture). The PCEs reported in this work (**Table 5** and **Table 6**) are much higher for dense architecture in comparison with mesoporous one (4.8% vs. 2.3 %).

The “dense” device shows higher  $J_{sc}$  values (17.5 mA/cm<sup>2</sup> (average:  $16.1 \pm 1.2$  mA/cm<sup>2</sup>)) in comparison with mesoporous architecture (8.5 mA/cm<sup>2</sup> (average:  $8.1 \pm 0.5$  mA/cm<sup>2</sup>)). The  $\text{Sb}_2\text{S}_3$  film has slightly better coverage and uniformity in the dense architecture. However, the amount of material is significantly higher in the mesoporous architecture. The literature states that a thickness of between 30 and 300 nm is appropriate considering the diffusion length of electron within the  $\text{Sb}_2\text{S}_3$ . [30] In addition, mesoporous TiO<sub>2</sub> should increase the interaction interface with  $\text{Sb}_2\text{S}_3$ , and thus increase the charge transfer paths between these two materials. But more importantly, it appears that glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> films have a preferential [hk0] orientation, whereas glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub> films have a preferential [hk1] orientation.

The decrease in efficiency is therefore mainly due to the [hk0] misorientation of the stibine crystals in the mesoporous architecture, resulting in poor charge transport and hence the observed decrease in  $J_{sc}$ .



Table 5 : Photovoltaic parameters of the best  $Sb_2S_3$  -based solar cells.

Sample	Solar simulator							
	Direct				Inverse			
	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)
Dense	0.531	16.2	43	3.7	0.551	17.5	50	4.8
Mesoporous	0.536	10.3	40	2.2	0.548	8.5	49	2.3

View Article Online  
DOI: 10.1039/D4EL00036FTable 6: Photovoltaic parameters of the  $Sb_2S_3$  -based solar cells (20 devices average)

Sample	Solar simulator								
		Direct				Inverse			
		Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)	Voc (V)	Jsc (mA/cm <sup>2</sup> )	FF	PCE (%)
Dense	<M>	0.487	16.1	44	3.5	0.523	15.8	49	4.1
	$\sigma$	0,020	1.2	2	0.4	0.019	1.1	2	0.5
Mesoporous	<M>	0.493	9.5	38	1.8	0.507	8.1	44	1.9
	$\sigma$	0.038	0.7	4	0.4	0.037	0.5	5	0.4

To further analyze the charge transfer properties of “dense” and “mesoporous” solar cells, EIS analyses were conducted. Results are presented as Nyquist plots in **Figure 14**. Data were fitted with the equivalent circuit model (inset) and are summarized in **Table 7**.

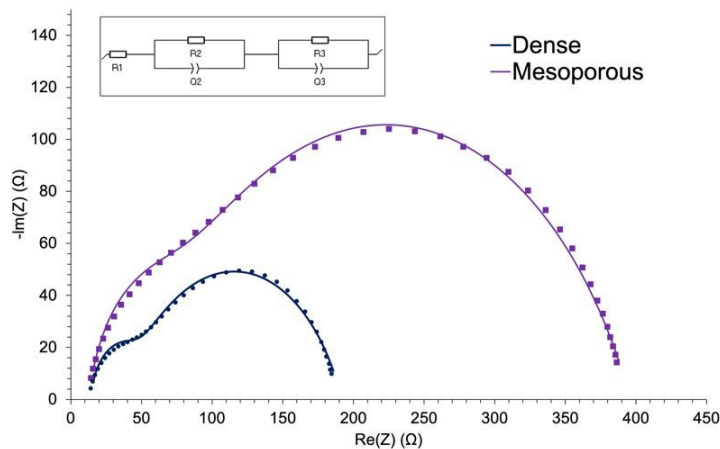


Figure 14: EIS Nyquist plots of glass/FTO/c- $TiO_2$ / $Sb_2S_3$ /Spiro/Au (dark blue) and glass/FTO/c- $TiO_2$ /mp- $TiO_2$ / $Sb_2S_3$ /Spiro/Au (purple) solar cells; Inset: equivalent electrical circuit used for data fitting.





Table 7 : Fitting resistance ( $R$ ) and constant phase element ( $Q$ ) parameters obtained from EIS data measured on glass/FTO/c-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub>/Spiro/Au and glass/FTO/c-TiO<sub>2</sub>/mp-TiO<sub>2</sub>/Sb<sub>2</sub>S<sub>3</sub>/Spiro/Au solar cells.

View Article Online  
DOI: 10.1039/D4EL00036F

	PCE (%)	$R_1$ [ $\Omega$ ]	$Q_2$ [ $10^{-3}$ F. s <sup>a-1</sup> ]	a	$R_2$ [ $\Omega$ ]	$Q_3$ [ $10^{-6}$ F. s <sup>b-1</sup> ]	b	$R_3$ [ $\Omega$ ]
Dense	4.8 %	14	11.51	1	28	2.075	0.732	150
Mesoporous	2.3%	12	11.15	1	46	1.820	0.702	339

A lower  $R_2$  value is obtained for dense architecture (28  $\Omega$ ) compared to the mesoporous (46  $\Omega$ ) device, corresponding to a more efficient charge transfer at the selective contact for the “dense” device. Usually, in perovskite solar cells, the mesoporous TiO<sub>2</sub> improves charge collection, resulting in a lower resistance  $R_2$  in the mesoporous architecture than in the dense one.[5], [41] However, in the case of stibine, the crystalline orientation has a non-negligible influence. Indeed, [hk1] orientation allows a better charge transport within layers, leading to improved charge collection at the electron selective contact and thus increased  $J_{sc}$  for the dense architecture.

The interfacial recombination resistance  $R_3$  of the mesoporous device (339  $\Omega$ ) is higher than  $R_3$  value of the dense device (150  $\Omega$ ). As the recombination rate at the Sb<sub>2</sub>S<sub>3</sub>/Spiro-OMeTAD interface is inversely proportional to  $R_3$ , it reveals faster interfacial recombination in dense device. In addition, a higher  $Q_3$  value is obtained for the dense device than for the mesoporous one, which means a higher accumulation of charges at the interface due to the absence of the mesoporous TiO<sub>2</sub> network increasing the electron extraction interface between stibine and ETL. Therefore, it can be assumed that more charges are transported into the stibine for the dense architecture thanks to its preferred [hk1] crystalline orientation, but that the smaller interface between stibine and dense TiO<sub>2</sub> leads to an accumulation of charges that can then undergo recombination.

All in all, EIS measurements corroborate J-V curves and the [hk0] misorientation of the stibine crystals in the mesoporous architecture has the greatest impact on the device efficiency, through  $J_{sc}$  decrease.



### 3. Conclusion

View Article Online  
DOI: 10.1039/D4EL00036F

$\text{Sb}_2\text{S}_3$  is a binary chalcogenide semiconductor which is abundant on earth, stable, non-toxic, and inexpensive. Therefore, scientists are particularly interested in this compound because of its excellent optoelectronic properties. Many studies have been carried out notably on the S/Sb ratio, concentrations, deposition speeds, doping etc. However, no studies comparing different precursors for  $\text{Sb}_2\text{S}_3$  stibine formation or the architecture (dense and mesoporous) of the assembled devices have been published to date.

This work reports for the first time the effect of the antimony precursor used for the  $\text{Sb}_2\text{S}_3$  film formation and the architecture of the cells on the preferential orientation of the stibine crystals. Indeed, as stibine shows anisotropic charge transfer properties, its crystalline orientation can directly impact the efficiency of the devices. A [hk1] crystal orientation reduces recombination, improves charge transport and is therefore desired for efficient PV devices.

In the first part of this study,  $\text{Sb}(\text{Ac})_3$  and  $\text{SbCl}_3$  were compared as antimony precursor. The  $\text{Sb}(\text{Ac})_3/\text{TU}$  solution allows the formation of films with higher coverage and uniformity than films obtained from the  $\text{SbCl}_3/\text{TU}$  solution. However, from PV efficiencies point of view it is not sufficient (4.9 % and 4.8% respectively) because the bandgap for  $\text{Sb}(\text{Ac})_3/\text{TU}$  (1.75 eV) is less favorable than for  $\text{SbCl}_3/\text{TU}$  (1.65 eV). In addition, the [hk0] crystalline orientation is more present in the  $\text{Sb}(\text{Ac})_3/\text{TU}$  films, which does not favor efficient charge transfer in the devices.

In the second part, the incorporation of a mesoporous  $\text{TiO}_2$  network in the device stack was considered to increase the quantity of  $\text{Sb}_2\text{S}_3$  photoactive material and improve the charge transfer in the devices. The morphology of the stibine (over)layer in the dense and mesoporous architectures is similar but slightly less covering in the case of mesoporous architecture, and it was proved that the stibine fills the  $\text{TiO}_2$  mesoporous network. Moreover, the measured bandgaps are similar (1.65 eV). However, the PV efficiencies are significantly lower in the case of the mesoporous architecture (2.3% vs. 4.8%), which can mainly be attributed to the [hk0] misorientation of the crystals leading to poor charge transport and therefore a decrease in  $J_{\text{sc}}$ .

This study highlights that a combination of three factors is crucial to boost  $\text{Sb}_2\text{S}_3$ -based device efficiencies: uniformity and coverage of the  $\text{Sb}_2\text{S}_3$  layer, adequate bandgap, and [hk1] crystalline orientation. This work therefore proves that properties careful examination and fine-tuning of these three properties are essential when working on  $\text{Sb}_2\text{S}_3$ -based solar cells and paves the way for further research on this area.

### 4. Acknowledgments


This work was supported by the Department of Chemistry of the University of Liège. The authors acknowledge Prof. Luc Henrard from University of Namur for XPS measurements and team members of GREENMat for additional technical and administrative support.




## 5. References

View Article Online  
DOI: 10.1039/D4EL00036F


- [1] Farhana M. A., Manjeevan A., and Bandara J., “Recent advances and new research trends in  $\text{Sb}_2\text{S}_3$  thin film based solar cells,” *Journal of Science: Advanced Materials and Devices*, 2023 vol. 8, no. 1. Elsevier B.V.
- [2] Barthwal S., Kumar R., and Pathak S., “Present Status and Future Perspective of Antimony Chalcogenide ( $\text{Sb}_2\text{X}_3$ ) Photovoltaics,” *ACS Applied Energy Materials*, 2022. vol. 5, no. 6. American Chemical Society, pp. 6545–6585, Jun. 27.
- [3] Shah U. A., Chen S., Khalaf G. M. G., Jin Z., and Song H., “Wide Bandgap  $\text{Sb}_2\text{S}_3$  Solar Cells,” *Advanced Functional Materials*, 2021. vol. 31, no. 27.
- [4] Deng H., Zeng Y., Ishaq M., Yuan S., Zhang H., Yang X., Hou M., Farooq U., Huang J., Sun K., Webster R., Whu H., Chen Z., Yi F., Song H., Hao X. and Tang J., “Quasiepitaxy Strategy for Efficient Full-Inorganic  $\text{Sb}_2\text{S}_3$  Solar Cells,” *Adv Funct Mater*, 2019.vol. 29, no. 31.
- [5] Jin X., Fang Y., Salim T., Feng M., Hadke S., Woei Leow S., Chien Sum T. and Wong L.H., “In Situ Growth of [hk1]-Oriented  $\text{Sb}_2\text{S}_3$  for Solution-Processed Planar Heterojunction Solar Cell with 6.4% Efficiency,” *Adv Funct Mater*, 2020 .vol. 30, no. 35.
- [6] Ennaceri H., Boujnah M., Taleb A., Khaldoun A., Sáez-Araoz R., Ennaoui A., El Kenz A., Benyoussef A., “ Thickness effect on the optical properties of  $\text{TiO}_2$  anatase thin films prepared by ultrasonic spray pyrolysis: Experimental and ab initio study”. *Int. J. Hydrogen Energy*, 2017,42, 19467-19480.
- [7] Zeng Y., Sun K., Huang J., Nielsen M.P., Ji F., Sha C., Yuan S., Zhang X, Yan C., Liu X., Deng H., Lai Y., Seidel J., Ekins-Daukes N., Liu F., Song H., Green M. and Hao X., “Quasi-Vertically-Orientated Antimony Sulfide Inorganic Thin-Film Solar Cells Achieved by Vapor Transport Deposition,” *ACS Appl Mater Interfaces*, 2020. vol. 12, no. 20, pp. 22825–22834.
- [8] Wu C., Zhang L., Che B., Xiao P., Yang J., Wang H., Chu L., Yan W. and Chen T., “The role of grain growth in controlling the crystal orientation of  $\text{Sb}_2\text{S}_3$  films for efficient solar cells,” *J Mater Chem A Mater*, 2023.vol. 11, no. 15, pp. 8184–8191.
- [9] You M. S., Lim C.-S., Kwon D. H., Heo J. H., Im S. H., and Chae K. J., “Oxide-free  $\text{Sb}_2\text{S}_3$  sensitized solar cells fabricated by spin and heat-treatment of  $\text{Sb(III)(thioacetamide)}_2\text{Cl}_3$ ,” *Org Electron*, 2015.vol. 21, pp. 155–159.
- [10] Choi Y. C. and Seok S. Il, “Efficient  $\text{Sb}_2\text{S}_3$ -sensitized solar cells via single-step deposition of  $\text{Sb}_2\text{S}_3$  using S/Sb-ratio-controlled  $\text{SbCl}_3$ -thiourea complex solution,” *Adv Funct Mater*, 2015 vol. 25, no. 19, pp. 2892–2898.
- [11] Wang X., Li J., Liu W., Yang S., Zhu C., and Chen T., “A fast chemical approach towards  $\text{Sb}_2\text{S}_3$  film with a large grain size for high-performance planar heterojunction solar cells,” *Nanoscale*, 2017. vol. 9, no. 10, pp. 3386–3390.
- [12] Gil E. K., Lee S.-J., Sung S.-J., Cho K. Y., and Kim D.-H., “Spin-Coating Process of an Inorganic  $\text{Sb}_2\text{S}_3$  Thin Film for Photovoltaic Applications,” *J Nanosci Nanotechnol*, 2016. vol. 16, no. 10, pp. 10763–10766.
- [13] Zheng L., Jiang K., Huang J., Zhang Y., Bao B., Zhou X., Wang H., Guan B., Yang L.M. and Song Y., “Solid-state nanocrystalline solar cells with an antimony sulfide absorber deposited by an in situ solid–gas reaction,” *J Mater Chem A Mater*, 2017. vol. 5, no. 10, pp. 4791–4796.
- [14] Tang R., Wang X., Jiang C., Li S., Liu W., Ju H., Yang S., Zhu C. and Chen T., “n-Type Doping of  $\text{Sb}_2\text{S}_3$  Light-Harvesting Films Enabling High-Efficiency Planar Heterojunction Solar Cells,” *ACS Appl Mater Interfaces*, 2018. vol. 10, no. 36, pp. 30314–30321.
- [15] Jiang C., Tang R., Wang X., Ju H., Chen G., and Chen T., “Alkali Metals Doping for High-Performance Planar Heterojunction  $\text{Sb}_2\text{S}_3$  Solar Cells,” *Solar RRL*, 2019. vol. 3, no. 1.
- [16] Tang R., Wang X., Jiang C., Li S., Jiang G., Yang S., Zhu C. and Chen T., “Vacuum assisted solution processing for highly efficient  $\text{Sb}_2\text{S}_3$  solar cells,” *J Mater Chem A Mater*, 2018. vol. 6, no. 34, pp. 16322–16327.



- [17] Guo C., Chen J., Li G., Liang X., Lai W., Yang L., Mai Y. and Li Z., “Enhanced Electrical Conductivity of Sb<sub>2</sub>S<sub>3</sub> Thin Film via C60 Modification and Improvement in Solar Cell Efficiency,” *Global Challenges*, 2019. vol. 3, no. 7.
- [18] Tamilselvan M., Byregowda A., Su C.-Y., Tseng C.-J., and Bhattacharyya A. J., “Planar Heterojunction Solar Cell Employing a Single-Source Precursor Solution-Processed Sb<sub>2</sub>S<sub>3</sub> Thin Film as the Light Absorber,” *ACS Omega*. 2019. vol. 4, no. 7, pp. 11380–11387.
- [19] Han J., Wang S., Yang J., Guo S., Cao Q., Tang H., Pu X., Gao B. and Li X., “Solution-Processed Sb<sub>2</sub>S<sub>3</sub> Planar Thin Film Solar Cells with a Conversion Efficiency of 6.9% at an Open Circuit Voltage of 0.7 V Achieved via Surface Passivation by a SbCl<sub>3</sub> Interface Layer,” *ACS Appl Mater Interfaces*, 2020. vol. 12, no. 4, pp. 4970–4979.
- [20] Wang S., Zhao Y., Che B., Li C., Chen X., Tang R., Gong J., Wang X., Chen G., Chen T, Li J. and Xiao X., “A Novel Multi-Sulfur Source Collaborative Chemical Bath Deposition Technology Enables 8%-Efficiency Sb<sub>2</sub>S<sub>3</sub> Planar Solar Cells,” *Advanced Materials*, 2022. vol. 34, no. 41.
- [21] Choi Y. C., Lee D. U., Noh J. H., Kim E. K., and Seok S. Il, “Highly improved Sb<sub>2</sub>S<sub>3</sub> sensitized-inorganic-organic heterojunction solar cells and quantification of traps by deep-level transient spectroscopy,” *Adv Funct Mater*, 2014. vol. 24, no. 23, pp. 3587–3592.
- [22] Zheng J., Liu C., Zhang L., Chen Y., Bao F., Liu J., Zhu H., Shen K., and Mai Y., “Enhanced hydrothermal heterogeneous deposition with surfactant additives for efficient Sb<sub>2</sub>S<sub>3</sub> solar cells,” *Chemical Engineering Journal*, 2022. vol. 446, p. 136474.
- [23] Li Y., Li R., Jia Z., Yu B., Yang Y., Bai S., Pollard M., Liu Y., Ma Y., Kampwerth H. and Lin Q., “Precursor Engineering of Solution-Processed Sb<sub>2</sub>S<sub>3</sub> Solar Cells,” *Small*, 2024. vol. 20, no. 10.
- [24] Maiti A., Chatterjee S., and Pal A. J., “Sulfur-Vacancy Passivation in Solution-Processed Sb<sub>2</sub>S<sub>3</sub> Thin Films: Influence on Photovoltaic Interfaces,” *ACS Appl Energy Mater*, 2020. vol. 3, no. 1, pp. 810–821.
- [25] Zhang L., Lian W., Zhao X., Yin Y., Chen T., and Zhu C., “Sb<sub>2</sub>S<sub>3</sub> Seed-Mediated Growth of Low-Defect Sb<sub>2</sub>S<sub>3</sub> on a TiO<sub>2</sub> Substrate for Efficient Solar Cells,” *ACS Appl Energy Mater*, 2020. vol. 3, no. 12, pp. 12417–12422.
- [26] Zhu L, Chen J., Liu R., Dong C., Yang S., Chen T., Chen C., Qiao Q. and Wang M., “Solution-Processed Compact Sb<sub>2</sub>S<sub>3</sub> Thin Films by a Facile One-Step Deposition Method for Efficient Solar Cells,” *Solar RRL*, 2021. vol. 5, no. 11.
- [27] Kondrotas R., Chen C., and Tang J., “Sb<sub>2</sub>S<sub>3</sub> Solar Cells,” *Joule*, 2018. vol. 2, no. 5. Cell Press, pp. 857–878.
- [28] Qiao S., Liu J., Li Z., Wang S., and Fu G., “Sb<sub>2</sub>S<sub>3</sub> thickness-dependent lateral photovoltaic effect and time response observed in glass/FTO/CdS/Sb<sub>2</sub>S<sub>3</sub>/Au structure,” *Opt Express*, 2017. vol. 25, no. 16, p. 19583.
- [29] Luz S.M., Del Tio J., Rocha G.J.M., Gonçalves A.R., Del’Arco A.P., “Cellulose and cellulignin from sugarcane bagasse reinforced polypropylene composites: Effect of acetylation on mechanical and thermal properties”, *Composites Part A: Applied Science and Manufacturing*, 2008. vol 39, Issue 9, pp. 1362-1369.
- [30] Li Z., Chen X., Zhu H., Chen J., Guo Y., Zhang C., Zhang W., Niu X. and Mai Y., “Sb<sub>2</sub>Se<sub>3</sub> thin film solar cells in substrate configuration and the back contact selenization,” *Solar Energy Materials and Solar Cells*, 2017. vol. 161, pp. 190–196.
- [31] Zhou Y., Wang L., Chen S., Qin S., Liu X., Chen J., Xue DJ., Luo M., Cao Y., Chen Y., Sargen E.H. and Tang J., “Thin-film Sb<sub>2</sub>Se<sub>3</sub> photovoltaics with oriented one-dimensional ribbons and benign grain boundaries,” *Nat Photonics*, 2015 vol. 9, no. 6, pp. 409–415.
- [32] Peng Z., Zheng Q., Wang R., Sun L., Wang H., Yuan Y., Xing Y., Yao L., Bi J. and Li W., “Controllable (HK1) Preferred Orientation of Sb<sub>2</sub>S<sub>3</sub> Thin Films Fabricated by Pulse Electrodeposition,” *SSRN Electronic Journal*, 2022.



- [33] Lv K., Shi C., Yang Y., Fu H., Guo F., and Wang Q., “The non-aqueous chemical bath deposition of  $\text{Sb}_2\text{S}_3$  thin films using  $\text{SbCl}_3$ -thioacetamide complex solution in DMF and the photovoltaic performance of the corresponding solar cells,” *Mater Lett*, 2019 vol. 256, p. 126636. View Article Online  
DOI: 10.1039/D4EL00036F
- [34] Liu R., Dong C., Zhu L., Chen J., Huang J., Cao W., Zhang X., Ge C., Yang S., Chen T. and Wang M., “Heteroepitaxial and homoepitaxial nucleation strategies to grow  $\text{Sb}_2\text{S}_3$  nanorod arrays and therefrom a derived gain of 7.18%-efficient  $\text{Sb}_2(\text{S},\text{Se})_3$  quasi- nanoarray heterojunction solar cells,” *Appl Mater Today*, 2022. vol. 27, p. 101487.
- [35] Zhang L., Wu C., Liu W., Yang S., Wang M., Chen T. and Zhu C., “Sequential deposition route to efficient  $\text{Sb}_2\text{S}_3$  solar cells,” *J Mater Chem A Mater*, 2018. vol. 6, no. 43, pp. 21320–21326.
- [36] Daem N., Dewalque J., Lang F., Maho A., Spronck G., Henrist C., Colson P., Stranks S.D. and Cloots R., “Spray-Coated Lead-Free  $\text{Cs}_2\text{AgBiBr}_6$  Double Perovskite Solar Cells with High Open-Circuit Voltage,” *Solar RRL*, 2021. vol. 5, no. 9.
- [37] Maho A., Lobet M., Daem N., Piron P., Spronck G., Loicq J., Cloots R., Colson P., Henrist C. and Dewalque J., “Photonic Structuration of Hybrid Inverse-Opal  $\text{TiO}_2$  Perovskite Layers for Enhanced Light Absorption in Solar Cells,” *ACS Applied Energy Materials*, 2021. vol 4 (2), 1108-1119
- [38] Daem N., Dewalque J., Kim D.K., Spronck G., Attwoord M., Wade J., Henrist C., Colson P., Heutz S., Cloots R. and Maho A., “Improved Photovoltaic Performances of Lead-Free  $\text{Cs}_2\text{AgBiBr}_6$  Double Perovskite Solar Cells Incorporating Tetracene as Co-Hole Transport Layer,” *Solar RRL*, 2023. vol. 7, no. 17.
- [39] Tress W., Leo K., and Riede M., “Optimum mobility, contact properties, and open-circuit voltage of organic solar cells: A drift-diffusion simulation study,” *Phys Rev B Condens Matter Mater Phys*, 2012 vol. 85, no. 15, pp. 1–11.
- [40] Chang J.A., Rhee J.H., Hyuk Im S., Lee Y.H., Kim H-J., Seok S., Nazeeruddin Md.K. and Grätzel M., “High-performance nanostructured inorganic-organic heterojunction solar cells,” *Nano Lett*, 2010. vol. 10, no. 7, pp. 2609–2612.
- [41] Gödel K.C., Chan Choi Y., Roose B., Sadhanala A., Snaith H.J., Seok S.II, Steiner U. and Pathak S.K., “Efficient room temperature aqueous  $\text{Sb}_2\text{S}_3$  synthesis for inorganic-organic sensitized solar cells with 5.1% efficiencies,” *Chemical Communications*, 2015. vol. 51, no. 41, pp. 8640–8643.
- [42] Choi Y. C., Lee D. U., Noh J. H., Kim E. K., and Seok S. II, “Highly improved  $\text{Sb}_2\text{S}_3$  sensitized-inorganic-organic heterojunction solar cells and quantification of traps by deep-level transient spectroscopy,” *Adv Funct Mater*, 2014. vol. 24, no. 23, pp. 3587–3592.



The authors confirm that the data supporting the findings of this study are available within the article.

[View Article Online](#)

DOI: 10.1039/D4EL00036F

Open Access Article. Published on 18 February 2025. Downloaded on 2/22/2025 5:18:13 AM.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

