

# EES Solar

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: E. H. Balaguera, F. J. Marinelli Pra, C. Das, L. Torresani, J. Bisquert and M. Saliba, *EES Sol.*, 2025, DOI: 10.1039/D5EL00137D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Broader context statement

View Article Online  
DOI: 10.1039/D5EL00137D

Perovskite solar cells have reached exceptional levels of power conversion efficiency; however, concerns about their long-term stability continue to hinder their roadmap toward commercial viability. A central issue among the degradation pathways is the behavior of mobile ions, recognized as the major contributor to the loss of efficiency and operational instability in perovskite photovoltaics. Illuminating the intricate multiscale dynamics of mobile ions is therefore pivotal for advancing standardized device characterization, elucidating degradation phenomena, enhancing operational stability, and propelling the broader adoption of this emerging photovoltaic technology. Characteristic times necessary to suppress ionic contributions during performance evaluations are investigated here through a systematic current transient analysis across a spectrum of voltage sweep rates. The temporal landscape governing ion dynamics of perovskites enables a quantitative distinction between steady-state and ‘ion-freeze’ efficiencies, offering a direct measure of degradation attributable to ionic motion. In this sense, a hysteresis domain is defined within a specific scan-rate interval. Theoretical insights are substantiated through Impedance Spectroscopy, reinforcing the interpretive framework. Collectively, our findings enrich the understanding of ionic behavior in perovskite materials and advocate for the integration of such methodologies into the toolkit for device characterization within the perovskite research community.



# 'Ion-freeze' efficiency in perovskite solar cells: Time scales for ion immobilization

View Article Online

DOI: 10.1039/D5EL00137D

Enrique H. Balaguera<sup>1,\*</sup>, F. Javier Marinelli Pra<sup>1</sup>, Chittaranjan Das<sup>2</sup>, Lorenzo Torresani<sup>2</sup>,  
Juan Bisquert<sup>3</sup>, and Michael Saliba<sup>2,\*</sup>

<sup>1</sup> Escuela Superior de Ciencias Experimentales y Tecnología, Universidad Rey Juan Carlos, C/ Tulipán, s/n, 28933 Móstoles, Madrid, Spain

<sup>2</sup> Institute for Photovoltaics (ipv), University of Stuttgart, Pfaffenwaldring 47, 70569 Stuttgart, Germany

<sup>3</sup> Instituto de Tecnología Química (Universitat Politècnica de València-Agencia Estatal Consejo Superior de Investigaciones Científicas), Av. dels Tarongers, 46022, València, Spain

*\*Corresponding author e-mails:*

[enrique.hernandez@urjc.es](mailto:enrique.hernandez@urjc.es), [michael.saliba@ipv.uni-stuttgart.de](mailto:michael.saliba@ipv.uni-stuttgart.de)

## Abstract

It is essential to shed light on the complex multiscale dynamics of mobile ions in perovskite solar cells for developing efficiency testing protocols, gaining a deeper understanding of the degradation mechanisms, improving long-term stability, and, ultimately, driving the commercialization of this technology. This study provides characteristic times for inhibiting the presence of mobile ions in efficiency measurements, enabling a comparison between 'ion-freeze' and steady-state efficiencies to quantify ion-induced degradation losses. Using current transient analysis during current-voltage measurements for a wide range of sweep rates, we achieve precise time-scale mapping of the complex ionic landscape of perovskites, spanning from ion immobilization (at time scales much shorter than the diffusion rate) to the equilibrium situation, encompassing the ubiquitous hysteresis effects for which we define a scan-rate range of occurrence. We corroborate the theory by using Impedance Spectroscopy. Our study provides valuable information about the intricate ionic dynamics in the context of classical current-voltage measurements, supporting the integration of these complementary experiments into the foundational characterization practices of the perovskite photovoltaic community.



## Introduction

Although perovskite solar cells hold significant potential to compete as strong contenders in the photovoltaic market due to the meteoritic growth in their power-conversion efficiency shown in recent years, the long-term stability of this technology is still behind that of commercially established silicon-based photovoltaics.<sup>1,2</sup> Specifically, metal halide perovskite solar cells are vulnerable to a range of stressors and can undergo multiple degradation mechanisms,<sup>3</sup> which can either be dominated by a single process or arise from the interplay of multiple competing factors.<sup>4</sup>

One of the most common underlying causes of these degradation pathways is the migration of mobile ions,<sup>5</sup> as an intrinsic property of the perovskite absorber material. However, this process can also have beneficial effects on freshly prepared or well-passivated photovoltaic devices.<sup>6,7</sup> Current-voltage characteristics are therefore compromised by transient ionic effects,<sup>8,9</sup> making their understanding crucial for minimizing changes in performance over time and, ultimately, the device optimization process.<sup>10</sup>

A new methodology to quantify mobile ion-induced efficiency losses to the device performance in perovskite photovoltaics was recently presented in literature using fast hysteresis measurements.<sup>11</sup> This technique allows one to determine the steady-state and the ‘ion-freeze’ efficiencies, as real and virtual metrics of the device performance, respectively.<sup>12</sup>

On the one hand, the steady-state efficiency  $\eta_{ss}$ , obtained from stabilized current-voltage curves, refers to the condition at which mobile ions are effectively in equilibrium and fully responding to the applied voltage.<sup>13</sup> It is achieved when the voltage sweep rate is substantially slower than the diffusion rate (a few hundred of mV/s). The ‘ion-freeze’ efficiency  $\eta_{ion-freeze}$ , on the other hand, represents the cell performance measured under conditions where the movement of mobile ions is effectively suppressed.<sup>11,12,14</sup> To effectively immobilize the ionic charges, the hold time along the stepwise scanning should be sufficiently short to assure that the mobile ions are “frozen” in time (ultra-fast scan rates in the sense of a few hundred of V/s).

The difference between fast and slow scan speeds, related, respectively, to ‘ion-freeze’ and steady-state efficiencies (that is,  $L_{ion} = \eta_{ion-freeze} - \eta_{ss}$ ), provides a value that quantifies the performance losses caused by mobile ions in perovskite solar cells.<sup>12</sup> Both limiting cases yield identical curves in the respective forward and reverse sweeps; however, hysteresis effects emerge in the current-voltage curves<sup>15</sup> at intermediate scan



speeds. The magnitude and rate of the ‘peak hysteresis’ or the maximum difference between the efficiency determined from the forward versus the reverse scan is a critical tool for the diagnosis of the relationship between ion migration dynamics and device performance.<sup>16-18</sup>

The origin and interpretation of hysteresis and the steady-state efficiency have been thoroughly addressed in the literature, thanks to extensive collaborative research efforts. However, there are still no consolidated theoretical principles that explain the internal physical processes behind the ‘ion-freeze’ current-voltage curves within realistic time scales that reflect the complex ionic behavior of metal halide perovskites.

In this work, we endorse the concept of ‘ion-freeze’ efficiency, inspired by the works of Stolterfoht and coworkers,<sup>5,11,12,14</sup> as a novel approach to be used as a key parameter for emerging characterization protocols in assessing ion-induced device performance losses of high-performance perovskite solar cells.

From current-voltage measurements at different scan rates, we first corroborate the experimental results provided by literature. Using an advanced stepwise transient analysis, we demonstrate that only the fast or pure component of the recombination processes affects the evolution of the ‘ion-freeze’ current-voltage curves.

If any part of this recombination shifts to the slow ion-controlled regime of recombination, the value of  $\eta_{\text{ion-freeze}}$  will change upon ageing. As the scan rate is reduced, the fast recombination mechanisms are complemented by ion-induced effects, including slow recombination processes, polarization mechanisms or even electric field screening, both in pristine conditions and after degradation.

We establish that the transition between consecutive current recordings in the voltage sweep is abruptly modified as a function of the speed rates and ageing time. From a physical model, we therefore explain the evolution of the experimental current-voltage curves, deciphering the time parameter that effectively leads to ion immobilization in a stepwise current-voltage scanning while further revealing the “game of dominance vs. loss of relevance” of physical effects in the current responses over time. A merit formula is derived to indicate the window of scan rates in which the experimentalists obtain current-voltage curves with hysteresis. Finally, impedance analysis was carried out for verification purposes.

## Experimental

### *Fabrication of perovskite solar cells*

View Article Online  
DOI: 10.1039/D5EL00137D



Pre-patterned glass/indium tin oxide (ITO) substrates were cleaned by immersion in 2% volume Mucosal in water, acetone, isopropyl alcohol (IPA), while sonicating for 15 minutes each time. After each step, the substrates are rinsed with the next solvent. The substrates are then dried with a N<sub>2</sub> flow before they undergo a 30-minute ultraviolet (UV)/ozone treatment. The electron transport layer (ETL) of tin(IV) oxide (SnO<sub>2</sub>) was deposited by spin coating (3000 rpm, 1000 rpm/s, 30 s) 100 µl of a 19 mg/mL solution in ethanol of SnCl<sub>2</sub>, that is later converted to SnO<sub>2</sub> by heating to 200 °C for 1 hour in air.

The triple-cation perovskite precursor was prepared by wet chemistry methods. From powder-based precursors, 800 mg of PbI<sub>2</sub> into 1157 µl of a 4:1 mix of dimethylformamide (DMF) and dimethylsulfoxide (DMSO), and 150 mg of PbBr<sub>2</sub> were dissolved into 272 µl of the solvent mix. Subsequently, 220 mg of formamidinium iodide (FAI) were dissolved into 1029 µl of the PbI<sub>2</sub> solution, and 20 mg of methylammonium bromide (MABr) were dissolved into 143 µl of the PbBr<sub>2</sub> solution. Finally, we mix 930 µl of the FAPbI<sub>3</sub> solution, 70 µl of MAPbBr<sub>3</sub> and 52.6 µl of a 40 mg/mL solution of cesium iodide (CsI) in DMSO. The solution is kept at rest in the dark before deposition. The 2,2',7,7'-tetrakis[*N,N*-di(4-methoxyphenyl)amino]-9,9'-spirobifluorene (Spiro-OMeTAD) solution was prepared by dissolving 92 mg of Spiro-OMeTAD powder into 1 ml of chlorobenzene, to which 21 µl of a 520 mg/ml solution of bis(trifluoromethanesulfonyl)lithium salt (LiTFSI) into acetonitrile, 15 µl of a 150 mg/ml Co(III) TFSI salt (CoTFSI) in acetonitrile and 32 µl of tributyl phosphate (TBP) were added.

The perovskite precursor (80 µl) was spin-coated on the glass/ITO/SnO<sub>2</sub> substrate in two steps, a slow step (1000 rpm, 1000 rpm/s, 10 s) and a fast step (5000 rpm, 2000 rpm/s, 30 s). The solvent was removed by dropping an antisolvent (240 µl of chlorobenzene) 5 seconds before the end of the last step. The layer was finalized by annealing at 100 °C for 30 minutes. The layers are cooled down to room temperature and a solution of phenyl ethyl ammonium iodide (PEAI) 10 mg/ml in 2-propanol (IPA) is dynamically spin coated (4000 rpm, 1000 rpm/s, 30 s) on the perovskite layer. A subsequent annealing at 100 °C for 1 minute ensures the formation of the 2D perovskite.

Spiro-OMeTAD was spin casted (4000 rpm, 2000 rpm/s, 30 s) on the perovskite layer after it cooled down. The samples were left to oxidize overnight. The 100 nm golden contacts were thermally evaporated on the stack to finalize the device.

### *Characterization protocols*






The current density-voltage curves for the perovskite solar cells were measured using a Keithley 2450 source meter under a standard Newport VeraSol-2 LED class AAA solar simulator. The lamp was calibrated using a NIST-certified KG3 filtered Si reference cell. The mask area was 0.16 cm<sup>2</sup> and the cells were measured at room temperature. We use scan rates from 1,000 V/s to 0.1 V/s to determine the hysteresis behavior.

Beyond electrical measurements were carried out with a PGSTAT302N potentiostat/galvanostat, equipped with an impedance and ultra-fast sampling module, FRA32M and ADC10M, respectively, from Metrohm AutoLab. Impedance measurements were carried out by configuring the AutoLab to apply sinusoidal signals of 10 mV amplitude from 1 MHz to 1 Hz at open-circuit voltage ( $V_{oc}$ ). On the other hand, chronoamperometric experiments were developed, immediately after frequency resolved measurements, by applying a constant signal with the value of  $V_{oc}$  and, after a long time, voltage-excited steps of 5 mV. A sampling rate of 10 MHz and 10 kHz was used to record the initial-decay fast region and the subsequent long tail of the current responses of perovskite solar cells, respectively.

All the experiments at room temperature were carried out under ambient atmosphere with the dry-air flow. The reproducibility of our conclusions was assured by conducting experiments in 10 samples with the same device configuration.

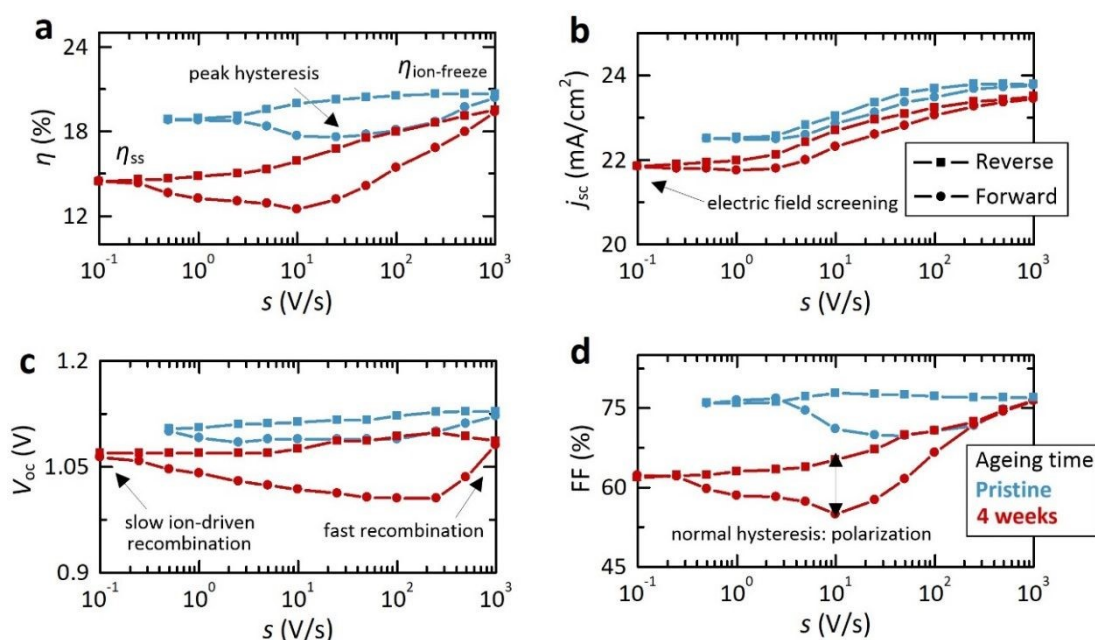

**Figure 1.** Exemplified trends of the (a) efficiency  $\eta$ , (b) short-circuit current density  $j_{sc}$ , (c) open-circuit voltage  $V_{oc}$ , and (d) fill factor (FF) obtained from the current-voltage curves at a wide range of scan rates in reverse (squares) and forward (circles) sweep directions for fresh and degraded perovskite devices.

## Results and discussion



### *Evolution of performance parameters as a function of the scan rate*

View Article Online  
DOI: 10.1039/D5EL00137D

To start with, we present representative performance data of a photovoltaic perovskite, reaching efficiencies up to 19%, with a *nip*-type configuration consisting of ITO/SnO<sub>2</sub>/perovskite (Cs<sub>0.05</sub>FA<sub>0.88</sub>MA<sub>0.07</sub>PbI<sub>2.79</sub>Br<sub>0.21</sub>)/PEAI/Spiro-OMeTAD/Au. We explore the impact of mobile ions on device degradation using the standardized dark storage protocol of ISOS-D-1 to obtain information on the cell's shelf life or the tolerance to ambient conditions.<sup>19</sup> Specifically, our samples were stored in the dark under ambient conditions, with a relative humidity ranging between 30 and 50%.

In the sequel, we use an 'ion-freeze' method that provides results of ion-induced losses by inhibiting the redistribution of mobile ions from their equilibrium positions at sufficiently high scan rates in comparison to equilibrium state. The evolution of the performance parameters of our perovskite solar cells with current-voltage sweep rate is shown in Figure 1: (a) efficiency  $\eta$ , (b) short-circuit current density  $j_{sc}$ , (c)  $V_{oc}$ , and (d) fill factor (FF).


Firstly, we detect in Figure 1a that the presence of mobile ions affects the device performance or 'ion-freeze' efficiency even when they are immobilized: Comparing  $\eta$  at ultra-fast scan and slow scan rates, a slight decrease is observed, attributed to an inhomogeneous redistribution throughout the perovskite active layer that influences the fast step of recombination.<sup>20</sup> This reduction of  $\eta_{ion-freeze}$  at fast scan rates (1,000 V/s) is minimal compared to the pronounced change of  $\eta_{ss}$  observed during ageing in the slow range of 1 V/s and 100 mV/s. As the samples degrade, the hysteresis effects also extend over a wider range of scan rates, evidencing a slower ionic response over time.<sup>10,21,22</sup> An additional indicator is the gradual shift of the 'peak hysteresis' towards slower scan rates, underscoring the strong dependence of hysteresis behavior on the degradation state of the device.<sup>23</sup>

Finally, it is important to point out that, for the fresh samples, the main reason for the ionic loss in efficiency is the decay of approximately 1 mA/cm<sup>2</sup> in  $j_{sc}$  (calculable from the comparison in equilibrium and 'ion-freeze' states). On the other hand, the performance losses for our degraded perovskite devices are fundamentally due to an abrupt decrease of FF.  $V_{oc}$  and  $j_{sc}$  are affected to a lesser extent. However, this evolution exemplifies a particular case of how the performance parameters of a *nip*-type cell can change during degradation. A more comprehensive and extensive review of such changes across a wide range of device layer architectures has already been conducted in the literature.<sup>12</sup> Next, we will analyze the case of a *pin*-type device.





As a representative example, Figure 2 shows the remarkable difference of the current-voltage curves and thus of the power conversion efficiency between fast and slow scan rates after 4 weeks of ageing. If one compares both ‘ion-freeze’ current-voltage curves of Figures 2a and 2c, fast losses can be easily obtained by inspection.<sup>12</sup> Conversely, ionic losses are observed when comparing the curves at fast and slow speeds<sup>11,12</sup> under the same operating conditions. Figures 2b and 2d show that hysteresis remains normal, not inverted, suggesting that capacitive and polarization effects<sup>24,25</sup> govern, for this case and commonly for high-performance and stable cells, the device operation.

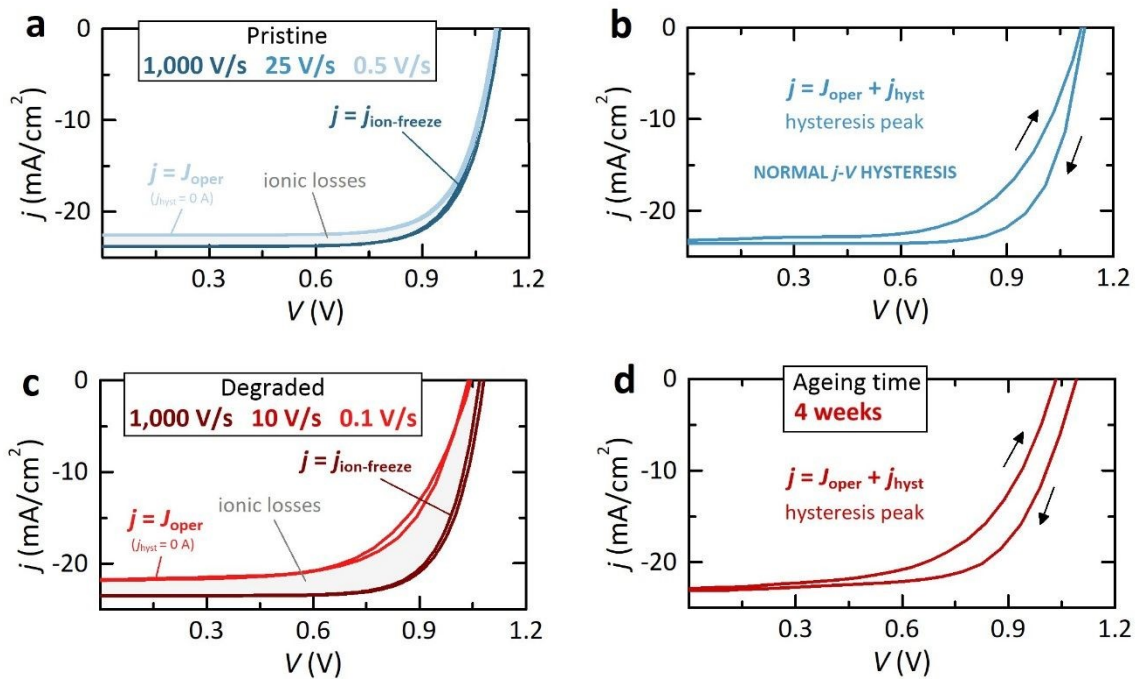

**Figure 2.** Representative scan rate-dependent current-voltage curves in (a,b) pristine conditions and (c,d) after 4 weeks of ageing. ‘Ion-freeze’ and steady-state current-voltage curves are obtained at fast (1,000 V/s in a and c) and slow sweep speeds (0.5 V/s in a and 0.1 V/s in c), respectively, at which the hysteresis disappears compared to intermediate rates (25 V/s in b and 10 V/s in d).

### Physical model of current-voltage curves in perovskite solar cells

To explain the experimental conditions that “freeze” the mobile ions during a stepwise voltage scanning, we propose a physical model that tracks the evolution of the current transient responses. The meaning of analytical variables is summarized in Table S1.

The basic solar cell device model establishes that the net extracted current in steady state or equilibrium is

$$J_{ss}(V) = J_{\text{rec}}(V) - J_{\text{ph}}(V, \Phi) \quad (1)$$



where  $J_{\text{rec}}$  and  $J_{\text{ph}}$  are, respectively, the stationary recombination current and the photocurrent in equilibrium created by charge generated per unit time and area under the incoming photon flux  $\Phi$ .

For perovskite solar cells,  $J_{\text{rec}}$  must be separated into two different pathways depending on the recombination velocity. Based on the experimental impedance observations of the voltage-dependence electrical elements reported in literature,<sup>26,27</sup> we therefore assume the overall recombination current as<sup>9,28</sup>

$$J_{\text{rec}}(V) = J_{\text{rec, fast}}(V) + J_{\text{rec, slow}}(V) \quad (2)$$

with

$$J_{\text{rec, fast}}(V) = J_{f0} e^{\frac{qV}{n_f k_B T}} \quad (3)$$

$$J_{\text{rec, slow}}(V) = J_{d0} e^{\frac{qV}{n_d k_B T}} \quad (4)$$

Both components represent, respectively, the fast bulk and slow surface recombination modes with  $J_{f0}$  and  $J_{d0}$  as pre-factors, as well as  $n_f$  and  $n_d$  as ideality factors. Here  $q$  is the elementary charge,  $k_B$  the Boltzmann's constant, and  $T$  the absolute temperature.

On the other hand, we also separate the photocurrent, created by charge extraction at selective contacts and commonly affected by ion-induced field screening in perovskite solar cells, into two components. The steady-state photocurrent  $J_{\text{ph}}(V, \Phi)$  is,

$$J_{\text{ph}}(V, \Phi) = j_{\text{ph0}}(\Phi) \left[ \eta_d + \eta_f \left( 1 - \frac{V}{V_0} \right) \right] \quad (5)$$

where  $j_{\text{ph0}}(\Phi)$  is a pre-factor,  $\eta_d$  is the efficiency of charge collection by diffusion (independent of the electric field),  $\eta_f$  is the efficiency of charge collection by drift transport,  $0 \leq (\eta_d + \eta_f) \leq 1$ , and  $V_0$  is a constant related to the built-in voltage. Logically,  $J_{\text{ph}} = j_{\text{ph0}}(\Phi)[\eta_d + \eta_f]$  at short-circuit conditions. However, the photocurrent is severely reduced during degradation,<sup>29,30</sup> generating a large disparity of current values close to 0 V due to charge collection issues.

In perovskite solar cells in which slow ion-assisted relaxation effects are present, an additional transient current  $j_{\text{trans}}$  is expected to be observed in experimental measurements. Thus, this fundamental analysis allows us to write a general formula for the total current<sup>31</sup> flowing through the perovskite solar cells  $j$  divided in terms accounting for electronic steady-state contributions and ion-assisted transient effects:

$$j = J_{\text{ss}} + j_{\text{trans}} \quad (6)$$



Note that we use uppercase letters for steady-state or instantaneous currents ( $J_{ss}$  and its terms) and lowercase letters for time-dependent currents ( $j_{trans}$  and its components) throughout the manuscript.

Ionic motion becomes evident at intermediate sweep rates, manifesting itself from hysteresis mechanisms in the current-voltage curves and underlying a multitude of phenomena, such as polarization,<sup>24, 32</sup> delayed recombination,<sup>32-34</sup> or field screening.<sup>12,29,35,36</sup> Consequently, the relaxation current can be expressed as:

$$j_{trans} = C_g \frac{dV}{dt} + j_{hyst} \quad (7)$$

including a displacement current that charges the geometrical capacitance of the perovskite material  $C_g$ , but insignificant for all purposes in this study, and the hysteresis current term

$$j_{hyst} = \underbrace{C_s \frac{dv_s}{dt}}_{\text{polarization}} - \underbrace{\tau_d \frac{dj_d}{dt}}_{\text{recombination}} + \underbrace{j_{ph0}(\Phi) \frac{\eta_f \tau_b}{V_0} \frac{dv_b}{dt}}_{\text{charge collection}} \quad (8)$$

divided in (i) a polarization current,  $C_s(dv_s/dt)$ , in the sense of a surface voltage  $v_s$  and a capacitance  $C_s$ ,<sup>32,37</sup> (ii) a current  $j_d$  associated to secondary recombination events,<sup>9,38-40</sup> and (iii) a residual charge collection current expressed in terms of  $v_b$  as the slow component of bulk electrical field (in terms of voltage). All the components of  $j_{hyst}$  are delayed by kinetic time constants ( $\tau_s$ ,  $\tau_d$ , and  $\tau_b$ , respectively) due to ionic mechanisms.<sup>41</sup> The respective relaxation equations of the ion-controlled processes given in eq 8 can be found in the Supporting Information.

Therefore, the limiting behavior of the hysteretic current is:

$$j_{hyst} = \begin{cases} 0 \text{ A}, & s \rightarrow 0 \\ C_{s0} \frac{V}{\tau_s} - J_{f0} e^{\frac{qV}{n_f k_B T}} + j_{ph0}(\Phi) \eta_f \frac{V}{V_0}, & s \rightarrow \infty \end{cases} \quad (9a)$$

$$(9b)$$

for steady-state and ‘ion-freeze’ conditions, respectively.

On the one hand, the hysteresis term is zero a sufficiently low scan rate ( $s \rightarrow 0$ ): Internal ionic dynamics are equilibrated ( $v_s \rightarrow V$ ,  $j_d \rightarrow J_{rec, slow}(V)$ , and  $v_b \rightarrow V$ ).<sup>13</sup>

Under ‘ion-freeze’ conditions (at a scan rate sufficiently high  $s \rightarrow \infty$ ), on the other hand, ionic polarization current is negligible ( $v_s \rightarrow 0$ ), surface recombination pathway is deactivated ( $j_d \rightarrow 0$ ),<sup>42</sup> and the charge collection efficiency by diffusion is not reduced ( $v_b \rightarrow 0$ ), generating, as discussed below, the difference between  $\eta_{ss}$  and  $\eta_{ion-freeze}$ . Note that eq 9b can be obtained, therefore, including a zero value for the slow ion-controlled



variables in eqs S1-S7. Specifically, it is important to clarify that surface recombination cannot dynamically respond during fast-hysteresis measurements (e.g., under ion-freeze conditions) when the applied voltage changes rapidly. The respective ion-driven current is consequently “frozen in time”, unchanged during the voltage scan, and therefore does not contribute to the observed current evolution. As a result, device efficiency remains invariant upon ageing. So, we demonstrate that the ‘ion-freeze’ efficiency is independent of surface recombination, as evidenced by both theory and experimental measurements via transient analysis and Impedance Spectroscopy. This insight resolves previously reported ambiguities arising from drift-diffusion approaches<sup>12</sup> and contributes to a deeper understanding of the ‘ion-freeze’ state in perovskite solar cells.

From eqs 1-6, 7, and 9b, the ‘ion-freeze’ current may be therefore expressed as

$$j_{\text{ion-freeze}} = J_{f0} e^{\frac{qV}{n_f k_B T}} + C_{s0} \frac{V}{\tau_s} - j_{\text{ph0}}(\Phi) [\eta_d + \eta_f] \quad (10)$$

In pristine conditions, the contributions of the ionic conductivity, the slow step of recombination and the bulk electric field, in terms of voltage, are negligible to the measured current  $j$  (Figure 1a), thus obtaining that  $j \sim j_{\text{ion-freeze}}$ .

#### *Transient analysis: ‘Ion-freeze’ conditions and hysteresis window*


A detailed examination of the experimental current-voltage curves in perovskite devices suggest that the shapes of the general responses are governed by the continuous voltage-dependent transient dynamics between the successive current recordings. Figure 3 illustrates a representative example of the intricate dynamics by which the current evolves between  $V_{\text{oc}}$  and  $V_{\text{oc}} + 5$  mV, from the step change to long time scales.

The resulting behavior is characterized by complex multiscale dynamics from the initial spike just after the voltage step, due to series resistance effects  $R_s$ , to the final steady-state regime, when the ions are in equilibrium. During this transition, the current response converges to an intermediate state, giving rise to the ‘ion-freeze’ phenomena in the current-voltage curves. Notably, the transient responses only show decays between 0 V and  $V_{\text{oc}}$  in our perovskite devices, driven primarily by polarization effects.<sup>24,43</sup> However, it is also plausible for the dynamics to exhibit a decay followed by a rise—or the reverse—accompanied by subsequent negative spikes,<sup>44</sup> if specific time constants are involved and delayed recombination or field screening become dominant factors.<sup>41</sup>

Figure 3 provides a general outlook of the current waveforms and the respective labels during the classical stepwise voltage scanning used to assess device efficiencies.<sup>45-47</sup> Note



that, however, the values of mainly the conductances and to a lesser extent the time constants can vary along the swept voltage due to the intrinsic nonlinear behavior of the solar cell and thus, further analysis is indeed necessary<sup>48</sup> as we will show below.

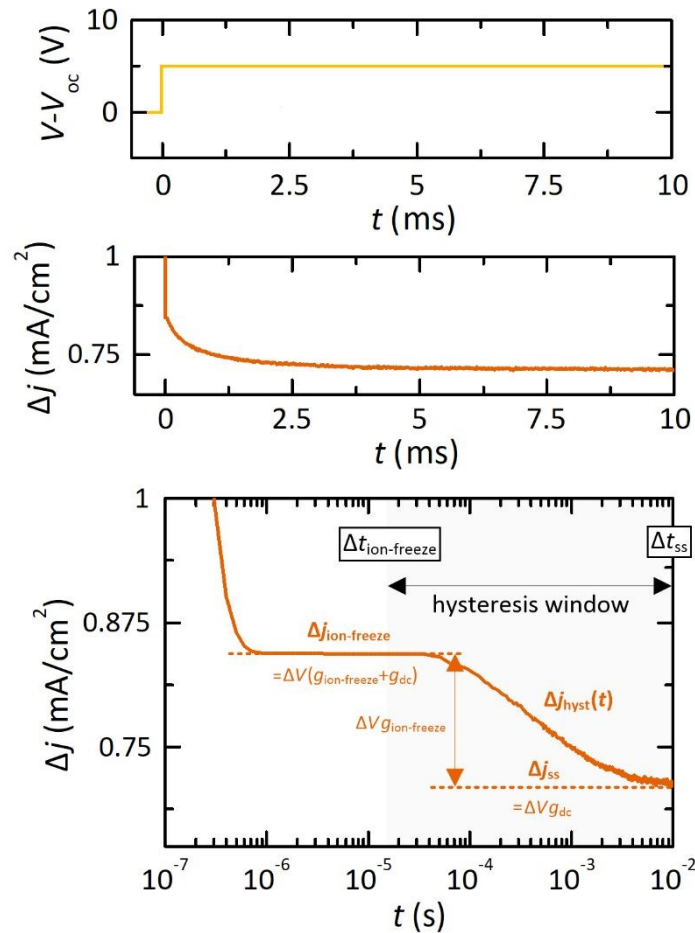

**Figure 3.** Experimental example of a small amplitude time-dependent photocurrent response  $\Delta j(t)$  during a stepwise voltage scanning. On the one hand, it is shown the voltage excitation  $\Delta V$ , consisting of a step-size of 5 mV from  $V_{oc}$  and, on the other hand, a representative ulterior current response in linear and logarithmic scales. The specific current values are highlighted at the relevant time scales.

To analyze the dynamical properties of the perovskite solar cells during classical voltage scanning from an adequate theoretical perspective, one should consider small step-type perturbations that depart from stationary points as excitations.<sup>45</sup> For the measurement of cyclic voltammetry, the critical parameter is the scan rate

$$s = \frac{\Delta V}{\Delta t} \quad (11)$$

and more specifically the time duration  $\Delta t$  of each step during the voltage sweep since  $\Delta V$  is certainly limited to maintain the linearity criteria (typically between 5 and 20 mV).  $s$  can be neither zero nor infinite as indicated by the eq 9, but a finite value sufficiently small or large dictated by  $\Delta t$ . By a close inspection of Figure 3, it is clear that the selection



of the parameter  $\Delta t$  plays a key role in the state of the current: equilibrated, hysteretic or in the 'ion-freeze' state.

From the linearization of eqs 1, 6, 7, and 8, network analysis and synthesis show that the relaxation processes involved in the current shifts  $\Delta j$  during a voltage sweep are described according to the following relationships:<sup>13, 42</sup>

$$\Delta j_{ss} = \Delta V(g_{rec, fast} + g_{rec, slow}) = \Delta V g_{dc} \quad (12)$$

$$\Delta j(t) = \Delta j_{ss} + \Delta j_{trans}(t) \quad (13)$$

$$\Delta j_{trans}(t) = \frac{\Delta V}{R_s} e^{-\frac{t}{\tau_v}} + \Delta j_{hyst}(t) \quad (14)$$

$$\Delta j_{hyst}(t) = \Delta V g_{ion-freeze} e^{-\frac{t}{\tau_{kin}}} \quad (15)$$

with  $\Delta j_{ss}$ ,  $\Delta j_{trans}(t)$ , and  $\Delta j_{hyst}(t)$  as the small signal current time domain variables. The state variables of our physical model establish several internal voltage-dependent conductances<sup>9</sup> in the perovskite devices that determine the transient responses (e.g.,  $g_{rec, fast}$ ,  $g_{rec, slow}$  or  $g_{ion-freeze}$  in eqs 12 and 15). The mathematical expression of such electrical terms can be found in Supporting Information.

The graphical representation of the experimental current shift  $\Delta j(t)$  of Figure 3 has been labeled to reveal details in correspondence to eqs 12-15. Here, the transient current makes a transition from the initial conductivity peak (with a value of  $1/R_s$  and after describing the dielectric capacitor charging governed by  $\tau_v = R_s C_g$ ) to an 'ion-freeze' conductivity state,  $g_{ion-freeze} + g_{dc}$ , that finally causes the current to decay by the ion-controlled effects towards a stationary conductance  $g_{dc}$ .

An expanded view of time-dependent photocurrents in response to stepwise voltage sweep in forward direction around  $V_{oc}$  of Figure 4a is shown in Figures 4b-d, as a representative example, for the perovskite devices after 4 weeks of ageing.

In the current-time profiles of Figure 4b, all photocurrents reach steady-state conditions at the end of each step and thus, no hysteresis effects should emerge in the subsequent current-voltage curves (refer to Figure 2c for a scan rate of 0.1 V/s). Here, we strategically select a minimum time delay  $\Delta t_{ss}$  to reach steady-state conditions:

$$\Delta t_{ss} = \left( 5 - \ln \left| \frac{g_{dc}}{g_{ion-freeze}} \right| \right) \tau_{kin} \quad (16)$$

obtained from the constraint of  $\Delta j_{ss} \gg \Delta j_{hyst}(\Delta t_{ss})$  with a 1% criterion.<sup>13,49</sup>


Subsequently the optimal scan rate  $s_{ss}$  to accelerate the elimination of the hysteresis is





$$s_{ss} = \frac{\Delta V}{\Delta t_{ss}} = \frac{\Delta V}{\tau_{kin}} \left[ 5 - \ln \left| \frac{g_{dc}}{g_{ion-freeze}} \right| \right]^{-1} \quad (17)$$

View Article Online  
DOI: 10.1039/D5EL00137D

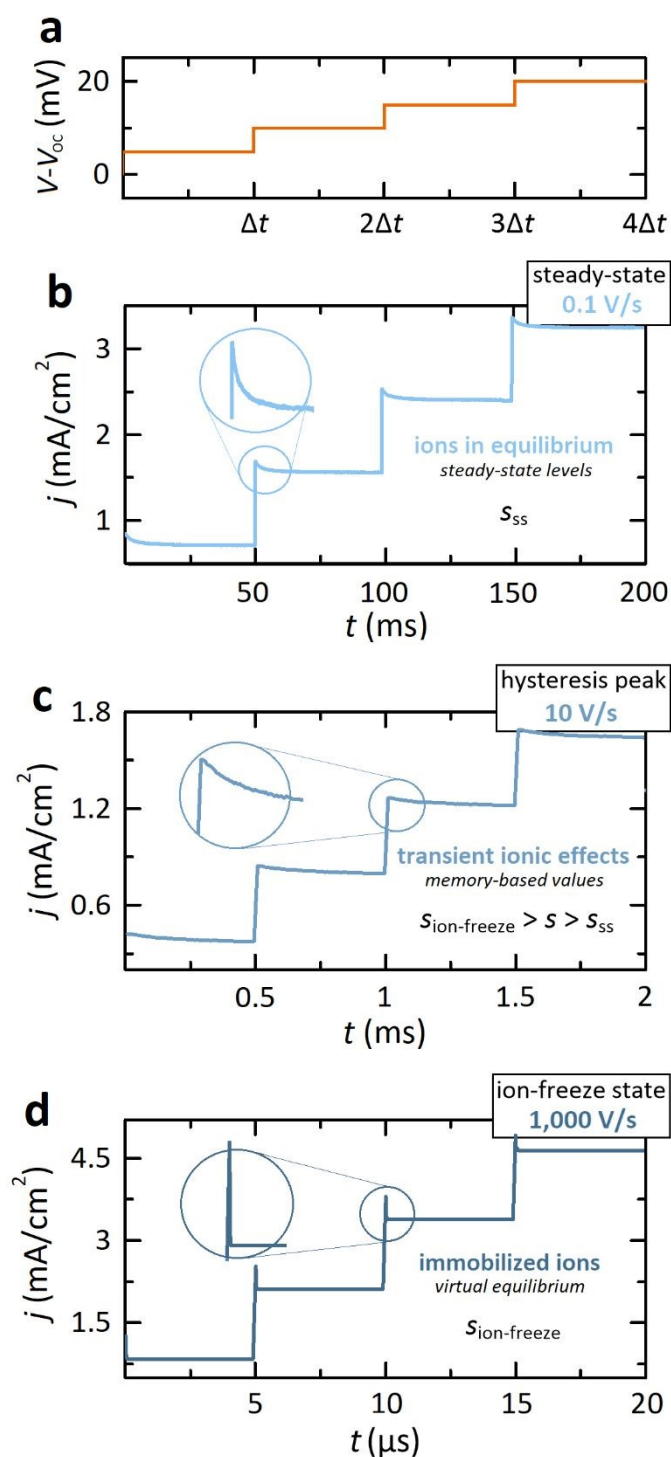

**Figure 4.** Illustrative photocurrent profile as a function of time at a forward stepwise voltage scan between  $V_{oc}$  and  $V_{oc} + 20$  mV depending on the duration of the 5-mV voltage steps: (a) 50 ms (scan rate of 0.1 V/s), (b) 0.5 ms (scan rate of 10 V/s), and (c) 5  $\mu$ s (scan rate of 1,000 V/s) corresponding, respectively, to the equilibrium situation, ‘peak hysteresis’, and ‘ion-freeze’ state of the current-voltage curves shown in Figures 2c and 2d for our perovskite devices.



Note that, to simplify the problem, we assumed that the slow physical processes exhibit approximately the same kinetic time constant  $\tau_{\text{kin}}$  independently on the voltage, which is a realistic assumption according to experimental observations.<sup>13,28,40</sup>

With lower experimental delay times, slow and non-steady-state operation of the *nip*-type perovskite solar cells gradually influence the electrical responses shown in Figure 4c. As a result, one obtains increasing residual currents as a natural consequence of the past activity. Physically speaking, the anomalous ion migration cannot respond as fast to each voltage stimuli introduced during cyclic voltammetry and therefore the current is interrupted before the value of the hysteretic current is negligible,  $\Delta j_{\text{hyst}}(t) \neq 0$  A. In this way, the shape of the current-voltage curve is altered due to the hysteresis phenomenon (refer to Figure 2d), driven by the presence of mobile ions.

Finally, Figure 4d shows that the pseudo-instantaneous currents uniquely emerge at sufficiently low values of  $\Delta t$ . Current responses are indeed pseudo-stabilized in an intermediate state in which the hysteretic response of eq 15 is constant,  $\Delta j_{\text{hyst}} = \Delta V g_{\text{ion-freeze}}$ , and thus the ions are immobilized without generating notorious discrepancies between the current-voltage relationship in forward and reverse scans (refer to Figure 2c for a scan rate of 1,000 mV/s). Only the charging of the bulk capacitor and the fast step of recombination processes take place at each voltage step during the voltage cycling. The key here is that the contribution of the ‘ion-freeze’ conductivity  $g_{\text{ion-freeze}}$  is not reduced by the respective exponential term of eq 15.

Mathematically speaking, this condition requires that  $e^{-t/\tau_{\text{kin}}} \sim 1$ , which implies that only the first term of the MacLaurin series expansion of the exponential function is operative,  $1 \gg (t/\tau_{\text{kin}})$ . Therefore, the time  $\Delta t_{\text{ion-freeze}}$  required to neutralize the movement of ions and approach an ‘ion-freeze’ state, in practice, is that for which

$$\Delta t_{\text{ion-freeze}} \ll \tau_{\text{kin}} \quad (18)$$

giving rise, at such time scales, to the ‘ion-freeze’ current:

$$\Delta j_{\text{ion-freeze}} = \Delta V (g_{\text{dc}} + g_{\text{ion-freeze}}) \quad (19)$$

By considering that the constraint of eq 18 is satisfied by selecting a value for  $\Delta t$  that is 100 times smaller than  $\tau_{\text{kin}}$ , a value of scan rate to suppress the ion mobility,  $s_{\text{ion-freeze}}$ , can be obtained as

$$s_{\text{ion-freeze}} = \frac{\Delta V}{\Delta t_{\text{ion-freeze}}} = 100 \frac{\Delta V}{\tau_{\text{kin}}} \quad (20)$$

being thus the optimal fast scan speed to obtain the ‘ion-freeze’ efficiency of perovskite solar cells. Note that we consider again the 1% criterion as in eqs 16 and 17.



Hence, the solar cell characterizers can obtain a current-voltage curve devoid of hysteresis effects at the voltage scan speeds given by eqs 17 and 20, corresponding to the equilibrium and ‘ion-freeze’ states, respectively. For intermediate values ( $\Delta t_{\text{ion-freeze}} < \Delta t < \Delta t_{\text{ss}}$ ), hysteresis phenomena become apparent in the current-voltage curves. Thus, this work, for the first time in literature, defines a “hysteresis window”

$$\frac{\Delta V}{\tau_{\text{kin}}} \left[ 5 - \ln \left| \frac{g_{\text{dc}}}{g_{\text{ion-freeze}}} \right| \right]^{-1} < s < 100 \frac{\Delta V}{\tau_{\text{kin}}} \quad (21)$$

that effectively enables a specific range of scan rates to observe hysteresis in the current-voltage characteristics of perovskite solar cells.

Note that, experimentally,  $\tau_{\text{kin}}$  does not maintain a strict constant value, particularly for aged devices throughout the swept voltage range, as can be seen in the plot of the relaxation times of Figure 5a obtained from time- and frequency-resolved techniques. This fact requires that experimentalists select an appropriate value based on the previously outlined rules: the maximum (minimum) value of  $\tau_{\text{kin}}$  for eqs 16 and 17 (eqs 18 and 20).

#### *Perspective of equivalent circuits: Impedance measurements*

Impedance analysis was also carried out for verification and illustrative purposes of the theory and the exemplificative decay time transient of Figure 3.

First, we present the theoretical admittance response of our model for a small sinusoidal perturbation of angular frequency  $\omega$ :


$$Y(j\omega) = g_{\text{dc}} + \frac{1}{R_s} \frac{j\omega}{j\omega + \frac{1}{\tau_v}} + \frac{j\omega g_{\text{ion-freeze}}}{j\omega + \frac{1}{\tau_{\text{kin}}}} \quad (22)$$

where, on the one hand, pure electronic processes are controlled by  $\tau_v$  and, on the other hand, slow ion-induced mechanisms are governed by the  $\tau_{\text{kin}}$ . For the previous results, it is clear that  $g_{\text{ion-freeze}} > 0$ .<sup>13</sup> Note that the ‘ion-freeze’ conductance could be lower than zero if negative capacitance features, in form of transient spikes<sup>44</sup> or inductive loops<sup>37,40,50-52</sup>, are present in the time- and frequency-resolved experiments, respectively.

We observe that the perovskite devices respond with a double capacitive arc in the complex plane impedance and admittance plots<sup>26,53</sup> of Figure 5b, which is strictly equivalent to the doubling decay of the current responses shown in Figures 3 and 4. Apart from the initial high frequency, there are two additional frequential values  $f_{\text{ion-freeze}}$  and  $f_{\text{dc}}$  (experimentally, around 100 kHz and 20 Hz) in which the admittance exhibits a single



conductance value with zero susceptance; i.e.,  $Y'(j\omega)$  is strictly equal to  $g_{\text{ion-freeze}}$  or  $g_{\text{dc}}$  and  $Y''(j\omega) = 0$ . Note that  $\omega = 2\pi f$ . There is, in fact, a close relationship between these frequencies and the values of time  $\Delta t_{\text{ion-freeze}}$  and  $\Delta t_{\text{ss}}$  leading to free-hysteresis current-voltage curves, as some of the authors indicated in a previous work.<sup>42</sup>

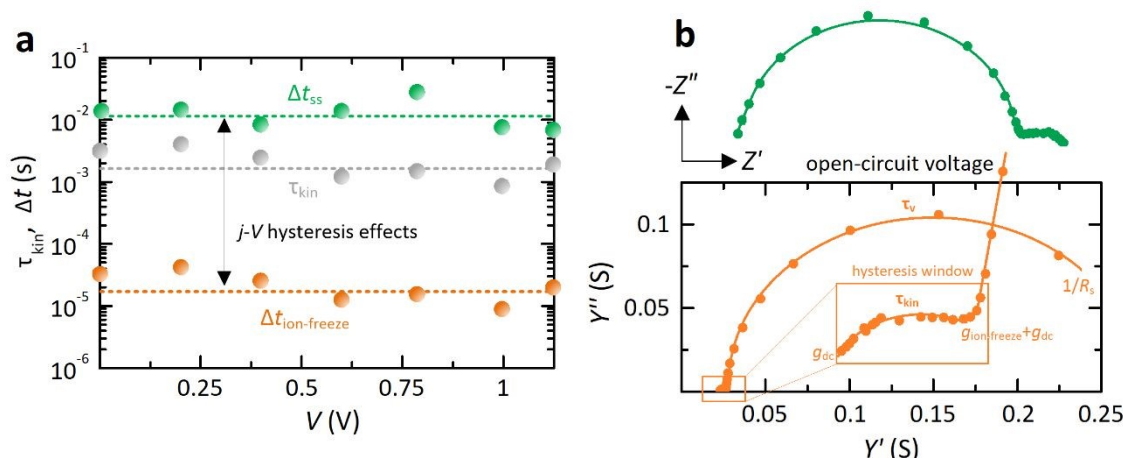

**Figure 5.** (a) Time constants extracted from the voltage-dependent transient and impedance responses. (b) Complex plane admittance spectrum measured at  $V_{\text{oc}}$  in a degraded device. Key conductance values are indicated in the experimental spectra to obtain a time-scale mapping of the current-voltage characteristics for perovskite solar cells: dc conditions, hysteresis window, and ‘ion-freeze’ state.

The hysteresis window is also highlighted in Figure 5a, which is located in the low-frequency range of  $f_{\text{ion-freeze}} > f > f_{\text{dc}}$ . To select such specific values, it is important to note that the concept of admittance, not impedance, must be analyzed, as only the former is controlled in voltage,<sup>41</sup> like the current-voltage curves. For a more detailed impedance-based analysis, additional measurements at different operating bias voltage points would be necessary, which have already been presented in detail by the authors in other works.<sup>49,54</sup>

#### *From nip- to pin-type cells in the experimental visualization of ‘ion-freeze’ regime*

Finally, it is important to point out that we also investigated *pin*-type devices (Figure S1), where we observed a similar evolution in the scan rate-dependent efficiency, current-voltage characteristics, transient current responses, and immittance spectra.

However, certain differences in the characteristic time scales are observed: the ‘ion-freeze’ state, the ‘peak hysteresis’, and the equilibrium regime occur at faster scan rates compared to our *nip*-type cells, which is consistent with previous reports.<sup>17,25,49</sup> Additionally, the ‘ion-freeze’ regime for this device is narrower (see, specifically, Figure S1c), an observation of particular interest. This peculiar behavior correlates with the



smaller separation between  $\tau_v$  and  $\tau_{kin}$  in the *pin*-type architecture relative to the *nip*-type device. In short, we present experimental evidence that confirms the validity of the conclusions presented here in the Supporting Information.

## Conclusions

This work reveals key physical characteristics of ion dynamics in perovskite solar cells, shedding light on the complex interplay between ionic motion and photovoltaic performance. By identifying characteristic timescales associated with ion immobilization, we establish the conditions under which ionic contributions to current-voltage behavior can be suppressed, enabling a direct quantification of ion-induced efficiency losses. Our findings encompass critical physical phenomena (including polarization effects, multi-timescale recombination dynamics, and electric field screening) that govern the energetic landscape of perovskites under operation. Notably, we identify for the first time a defined “hysteresis window”, a specific scan-rate range in which mobile ion motion gives rise to observable current-voltage hysteresis, thereby linking ion kinetics to measurable device behavior. These insights are supported through complementary experimental techniques such as cyclic voltammetry, chronoamperometry, and impedance spectroscopy, applied to high-performance perovskite devices. Together, these results offer a refined physical understanding of time-dependent ionic processes, providing a foundation for improved efficiency characterization and stability strategies in perovskite photovoltaics.

## Associated content

*Supporting information.* Theory of ion-controlled processes of perovskite solar cells; conductances of the complete device model; summary of analytical variables; application in *pin*-type cells.

## Conflict of interests

There are no conflicts to declare.

## Acknowledgements

This work has received funding from the Universidad Rey Juan Carlos, project numbers M3704 and M3712. J. Bisquert thank Grant EUR2022-134045 funded by MICIU/AEI/10.13039/501100011033 and European Union NextGenerationEU/PRTR.



## References

View Article Online  
DOI: 10.1039/D5EL00137D

- 1 N.-G. Park, M. Grätzel, T. Miyasaka, K. Zhu and K. Emery, *Nat. Energy*, 2016, **1**, 16152.
- 2 Y. Rong, Y. Hu, A. Mei, H. Tan, M. I. Saidaminov, S. I. Seok, et al., *Science*, 2018, **361** (6408), eaat8235.
- 3 W. Meng, K. Zhang, A. Osvet, J. Zhang, W. Gruber, et al., *Joule*, 2022, **6** (2), 458–475.
- 4 L. Meng, J. You, Y. Yang, L. Meng, J. You, et al., *Nat. Commun.*, 2018, **9**, 5265.
- 5 J. Thiesbrummel, V. M. Le Corre, F. Peña-Camargo, L. Perdigón-Toro, F. Lang, et al. *Adv. Energy Mater.*, 2021, **11** (34), 202101447.
- 6 J. A. Kress, C. Quarti, Q. An, S. Bitton, N. Tessler, et al., *ACS Energy Lett.*, 2022, **7** (10), 3302–3310.
- 7 L. J. F. Hart, F. J. Angus, Y. Li, A. Khaleed, P. Calado, et al. *Energy Environ. Sci.*, 2024, **17** (19), 7107–7118.
- 8 E. L. Unger, E. T. Hoke, C. D. Bailie, W. H. Nguyen, A. R. Bowring, et al., *Energy Environ. Sci.*, 2014, **7**, 3690–3698.
- 9 E. H. Balaguera and J. Bisquert, *Small*, 2025, **21** (2), 202409534.
- 10 W. Tress, N. Marinova, T. Moehl, S. M. Zakeeruddin, M. K. Nazeeruddin, et al., *Energy Environ. Sci.*, 2015, **8**, 995–1004.
- 11 V. M. Le Corre, J. Diekmann, F. Peña-Camargo, J. Thiesbrummel, N. Tokmoldin, et al., *Sol. RRL* 2022, **6** (4), 2100772.
- 12 J. Thiesbrummel, S. Shah, E. Gutierrez-Partida, F. Zu, F. Peña-Camargo, et al., *Nat. Energy*, 2024, **9**, 1–13.
- 13 E. H. Balaguera and J. Bisquert, *ACS Energy Lett.*, 2024, **9** (2), 478–486.
- 14 J. Diekmann, F. Peña-Camargo, N. Tokmoldin, J. Thiesbrummel, J. Warby, et al., *J. Phys. Chem. Lett.*, 2023, **14** (18), 4200–4210.
- 15 H. J. Snaith, A. Abate, J. M. Ball, G. E. Eperon, T. Leijtens, et al., *J. Phys. Chem. Lett.*, 2014, **5** (9), 1511–1515.
- 16 S. van Reenen, M. Kemerink and H. J. Snaith, *J. Phys. Chem. Lett.*, 2015, **6** (19), 3808–3814.
- 17 P. Calado, A. M. Telford, D. Bryant, X. Li, J. Nelson, et al., *Nat. Commun.*, 2016, **7** (1), 13831.
- 18 M. T. Neukom, S. Züfle, E. Knapp, M. Makha, R. Hany, et al., *Sol. Energy Mater. Sol. Cells*, 2017, **169**, 159–166.





- 19 M. V. Khenkin, E. A. Katz, A. Abate, G. Bardizza, J. J. Berry, et al., *Nat. Energy*, 2020, **5** (1), 35–49. View Article Online  
DOI: 10.1039/D5EL00137D
- 20 A. Pockett, and M. J. Carnie, *ACS Energy Lett.*, 2017, **2** (7), 1683–1689.
- 21 D. A. Jacobs, Y. Wu, H. Shen, C. Barugkin, F. J. Beck, et al., *Phys. Chem. Chem. Phys.*, 2017, **19** (4), 3094–3103.
- 22 C. Eames, J. M. Frost, P. R. F. Barnes, B. C. O'Regan, A. Walsh, et al., *Nat. Commun.*, 2015, **6** (1), 7497.
- 23 D.-H. Kang and N.-G. Park, *Adv. Mater.*, 2019, **31** (34), 201805214.
- 24 B. Chen, M. Yang, X. Zheng, C. Wu, W. Li, et al., *J. Phys. Chem. Lett.*, 2015, **6** (23), 4693–4700.
- 25 E. Hernández-Balaguera, B. Romero, B. Arredondo, G. del Pozo, M. Najafi, et al., *Nano Energy*, 2020, **78**, 105398.
- 26 I. Zarazua, G. Han, P. P. Boix, S. Mhaisalkar, F. Fabregat-Santiago, et al., *J. Phys. Chem. Lett.*, 2016, **7** (24), 5105–5113.
- 27 O. Almora, K. T. Cho, S. Aghazada, I. Zimmermann, G. J. Matt, et al., *Nano Energy*, 2018, **48**, 63–72.
- 28 C. Gonzales, A. Guerrero and J. Bisquert, *J. Phys. Chem. C*, 2022, **126** (32), 13560–13578.
- 29 A. Schiller, S. Jenatsch, B. Blülle, M. A. T. Cachafeiro, F. Ebadi, et al., *J. Phys. Chem. Lett.*, 2024, **15** (45), 11252–11258.
- 30 W. Clarke, P. J. Cameron and G. Richardson, *J. Phys. Chem. Lett.*, 2024, **15** (47), 11730–11736.
- 31 J. Bisquert, *Adv. Energy Mater.*, 2024, **14** (26), 202400442.
- 32 S. Ravishankar, O. Almora, C. Echeverría-Arrondo, E. Ghahremanirad, C. Aranda, et al., *J. Phys. Chem. Lett.*, 2017, **8** (5), 915–921.
- 33 A. O. Alvarez, R. Arcas, C. A. Aranda, L. Bethencourt, E. Mas-Marzá, et al., *J. Phys. Chem. Lett.*, 2020, **11** (19), 8417–8423.
- 34 W. Tress, J. P. C. Baena, M. Saliba, A. Abate and M. Graetzel, *Adv. Energy Mater.*, 2016, **6** (19), 1600396.
- 35 M. Diethelm, T. Lukas, T.; J. Smith, A. Dasgupta, P. Caprioglio, et al., *Energy Environ. Sci.*, 2025, **18** (3), 1385–1397.
- 36 R. A. Belisle, W. H. Nguyen, A. R. Bowring, P. Calado, P.; Calado, P.; X. Li, et al., *Energy Environ. Sci.*, 2017, **10** (1), 192–204.



- 37 E. Ghahremanirad, A. Bou, S. Olyaei and J. Bisquert, *J. Phys. Chem. Lett.*, 2017, **8** (7), 1402–1406.
- 38 J.-P. Correa-Baena, S.-H. Turren-Cruz, W. Tress, A. Hagfeldt, C. Aranda, et al., *ACS Energy Lett.*, 2017, **2** (3), 681–688.
- 39 A. Guerrero, G. Garcia-Belmonte, I. Mora-Sero, J. Bisquert, Y. S. Kang, et al., *J. Phys. Chem. C*, 2016, **120** (15), 8023–8032.
- 40 F. Ebadi, N. Taghavinia, R. Mohammadpour, A. Hagfeldt and W. Tress, *Nat. Commun.*, 2019, **10**, 1574.
- 41 E. Hernández-Balaguera and J. Bisquert, *Adv. Funct. Mater.*, 2024, **34** (6), 202308678.
- 42 E. H. Balaguera and J. Bisquert, *Energy & Fuels*, 2025, **39** (7) 3638–3648.
- 43 E. Hernández-Balaguera, G. del Pozo, B. Arredondo, B. Romero, C. Pereyra, et al., *Sol. RRL*, 2021, **5** (4), 202000707.
- 44 E. Hernández-Balaguera and J. Bisquert, *ACS Energy Lett.*, 2022, **7** (8), 2602–2610.
- 45 H.-S. Kim and N.-G. Park, *J. Phys. Chem. Lett.*, 2014, **5** (17), 2927–2934
- 46 E. Hernández-Balaguera, B. Arredondo, G. del Pozo, B. Romero, *Commun. Nonlinear Sci. Numer. Simulat.*, 2020, **90**, 105371.
- 47 J. Bisquert, *PRX Energy*, 2024, **3**, 011001.
- 48 A. Guerrero, J. Bisquert and G. Garcia-Belmonte, *Chem. Rev.*, 2021, **121**, 14430–14484.
- 49 E. Hernández-Balaguera, L. Muñoz-Díaz, C. Pereyra, M. Lira-Cantú, M. Najafi, et al., *Mater. Today Energy*, 2022, **27**, 101031.
- 50 J. Bisquert and A. Guerrero, *J. Am. Chem. Soc.*, 2022, **144** (13), 5996–6009.
- 51 E. Hernández-Balaguera, B. Arredondo, C. Pereyra and M. Lira-Cantú, *J. Power Sources*, 2023, **560**, 232614.
- 52 C. A. Aranda, A. O. Alvarez, V. S. Chivrony, C. Das, M. Rai, et al., *Joule*, 2024, **8** (1), 241–254.
- 53 E. Hernández-Balaguera, B. Romero, M. Najafi, Y. Galagan, *Adv. Mater. Interfaces*, 2022, **9** (9), 202102275.
- 54 J. Bisquert, A. Guerrero and C. Gonzales, *ACS Phys. Chem. Au*, 2021, **1** (1), 25–44.

View Article Online  
DOI: 10.1039/D5EL00137D



**Data availability statement**

[View Article Online](#)  
DOI: 10.1039/D5EL00137D

The data that support the findings of this study are available from the corresponding authors, upon reasonable request.

