Green Chemistry



PAPER

View Article Online



Cite this: Green Chem., 2025, 27.

Chemical looping hydrogen production from ammonia and water: materials and technoeconomics†

Amirmohammad Arjomand Kermani, Kyle Shank and Shang Zhai 🕩 *a,b

Ammonia (NH₃) is a promising hydrogen carrier due to high hydrogen density and established infrastructure. We present a novel chemical looping process to produce H2 from NH3 oxidation and decomposition and from water splitting, integrating thermochemical redox looping and catalytic reaction. Unlike singlestep catalytic NH3 decomposition, the looping configuration produces high purity H2 from the water splitting that significantly lowers separation energy and cost. FeOx/YSZ and FeO5CO5COX/YSZ were shown as durable dual-functional oxygen carriers and catalysts, achieving 95% and 99% NH₃ conversion and 39% and 25% water splitting conversion, respectively. The materials' redox capacities were explained by simultaneous Fe and Co redox reactions and solid-state phase transition between metal (alloy) and spinel. From 450 to 600 °C, Fe redox capacity increased, while Co redox capacity decreased. Kinetic limitations hindered full reduction of FeO_x/YSZ to metallic Fe at 450 °C due to lack of the effective Co catalyst, while thermodynamic limitations prevented complete oxidation of Co metal in Fe_{0.5}Co_{0.5}O_x/YSZ. Technoeconomic analysis showed the looping process achieves 52% to 86% lower energy and equipment costs than single-step catalytic NH₃ decomposition with different H₂ separation methods.

Received 15th January 2025, Accepted 21st May 2025 DOI: 10.1039/d5qc00236b

rsc.li/greenchem

Green foundation

- 1. This paper presents a novel process of chemical looping ammonia oxidation and decomposition integrated with water splitting (CLAOD-WS). Compared to single-step catalytic NH3 decomposition, CLAOD-WS gives high purity H2 to significantly lower separation energy and cost, enabling NH3 as a promising
- 2. FeOx/YSZ and Fe_{0.5}Co_{0.5}Ox/YSZ were shown as durable dual-functional oxygen carriers and catalysts. The materials' redox capacities were explained by simultaneous Fe and Co redox reactions and solid-state phase transition between metal (alloy) and spinel. The looping process achieves 52% to 86% lower energy and equipment costs than single-step catalytic NH3 decomposition.
- 3. Future research can include reactor design and materials chemistry to co-optimize oxygen exchange capacity and catalytic reactivity, so that almost all H2 is produced from water splitting step rather than NH3 conversion step, further lowing H2 separation energy and cost.

Introduction

Addressing the Gigaton-scale greenhouse gas (GHG) emissions challenge is critical for mitigating global warming. 1 Clean hydrogen (H₂) produced without GHG emissions offers significant potential to support carbon neutrality, especially in hardto-decarbonize including industry

transportation.^{2,3} Its applications span chemical feedstock, steel production, fuel for heavy-duty transport, industrial/domestic heating, and renewable energy storage.^{2,3} To expand clean H₂ utilization, the issue of energy-intensive and costly H₂ delivery needs to be overcome.^{1,4} The current cost to produce GHG-free H₂ with water electrolysis is about \$4-5 per kg,5 while the average cost of transporting and dispensing H₂ can range from \$8.17-\$9.46 per kg for gaseous tube trailers and \$8.31-\$11.35 per kg for liquid tankers,6 mainly because H₂ compression and liquefaction are expensive and energyintensive.⁷⁻¹¹ Chemical hydrogen carriers have the potential to help lower energy demand and cost for H₂ delivery. 1,4,12

NH₃ proves to be an excellent hydrogen carrier. Firstly, it possesses a high volumetric and gravimetric hydrogen density compared to several well-known hydrogen carriers (Fig. 1a). 1,12,13 At 298 K and 1 MPa, the volumetric hydrogen density of NH₃ is

^aDepartment of Mechanical and Aerospace Engineering, The Ohio State University, 201 West 19th Ave, Columbus, OH 43210, USA. E-mail: zhai.218@osu.edu ^bSchool of Earth Sciences, The Ohio State University, 125 South Oval Mall, Columbus, OH 43210, USA

[†] Electronic supplementary information (ESI) available: Experimental methods, data analysis methods and results, additional looping performance data, equilibrium simulation method, energy and technoeconomic analysis methods. See DOI: https://doi.org/10.1039/d5gc00236b

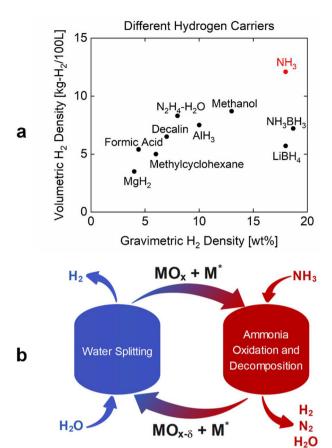


Fig. 1 (a) Comparison among chemical hydrogen carriers for volumetric and gravimetric hydrogen densities at 0.1 MPa and 240 K. Adapted from references. $^{1,12,13,17-20}$ (b) Chemical looping ammonia oxidation and decomposition integrated with water splitting (CLAOD-WS) process schematic. MO_x is a redox active metal oxide, and M* is a metallic catalyst. Compositions of M and M* may change between the reduced and oxidized states.

60 times that of H₂, and the storage cost of NH₃ is only 3% of H₂.¹ Secondly, NH₃ is vastly utilized as a fertilizer in agriculture; consequently, well-established infrastructure exists in many countries.¹⁴ NH₃ has been easily and safely transported *via* pipelines, trucks, and rail cargos for many decades.^{1,15,16}

Catalytic NH₃ decomposition to H₂ has been extensively studied and catalysts such as noble metals of ruthenium (Ru) and platinum (Pt) or transition metal-based catalysts of nickel (Ni), cobalt (Co), and iron (Fe) have been investigated to give high conversions (>95%) at moderate temperatures (450–600 °C). 4.21–24 In a study on noble metal catalysts by Yao et al., high NH₃ conversion of 96% was achieved at the moderate temperature of 500 °C using nanoparticles of Ru on silica (SiO₂) support. A In a comprehensive study by Gu et al., Co, Ni, and Fe were synthesized on alumina (Al₂O₃) support, with catalytic NH₃ decomposition at 600 °C revealing conversion rates of 100%, 93%, and 86% for Co, Ni, and Fe catalysts, respectively. Xie et al. tuned CoMoFeNiCu high entropy alloy catalyst nanoparticles dispersed on carbon nanofibers which reached 100% conversion of NH₃ at 525 °C for Co₂₅Mo₄₅Fe₁₀Ni₁₀Cu₁₀.

This was compared to bimetallic Co–Mo and monometallic Ru which only reached 46% and 73% conversion, respectively, at 600 °C. Tabassum *et al.* present a Ru-free catalyst composed of a CoNi alloy supported on a K-promoted MgO–CeO₂–SrO mixed oxide, achieving nearly complete NH₃ conversion at 450 °C. The catalyst demonstrates high stability and hydrogen production rates comparable to Ru-based catalysts, highlighting the role of metal–oxide interfaces and promoter effects in enhancing activity and stability. ²¹

Oxygen carrier metal oxides have been researched for NH3 oxidation to nitrogen (N2) and nitrogen oxides (NOx). Normann et al. introduced a chemical looping scheme in which NH3 was oxidized using Fe, manganese (Mn), and Nibased oxygen carriers; afterwards, the oxygen carriers were reoxidized by oxygen.²⁵ This work focused on the production of nitric oxide (NO) and H2O from NH3 oxidation and concluded that Mn-based oxide demonstrates the best performance in NO formation. In another study, Cheng et al. investigated NH3 oxidation to NO_x and N₂ using Ilmenite (iron-titanium oxide).26 It was discovered that decreasing NH3 concentration decreases the selectivity of NH₃ decomposition toward N₂ and increases that toward NO formation. Ruan et al. investigated a chemical looping scheme in which NH3 was selectively oxidized to form NO using a vanadium pentoxide (V2O5) oxygen carrier and then the oxygen carrier was re-oxidized using oxygen gas (O2).27 This configuration achieved over 95% NH3 conversion and 100% NO selectivity at 650 °C.

Oxygen carriers have also been studied in thermochemical redox cycles for H₂ production by water splitting. ²⁸⁻⁴³ The oxygen capacity of the carrier materials comes from either solid phase transformation or oxygen vacancy. One category of the redox cycles uses high temperature to thermally reduce the oxygen carrier. Zhai et al. utilized mixed metal oxides called poly-cation oxides (PCOs) which consist of transition metals Fe, Mg, Co, and Ni. Fe redox in the PCOs provided the redox capacity, while the other redox inactive metals helped tune the oxide phase transformation to lower the reduction reaction temperature for a lower system cost. 28 Tran et al. examined the performance of iron aluminate ((Fe_{0.33}Al_{0.67})_{3-δ}O₄) for H₂O and CO₂ splitting reactions. Thermal reduction at 1400 °C was followed by oxidation at elevated pressures (1-10 atm), resulting in enhanced equilibrium extent and reaction kinetics.38 Wexler et al. presented a newly developed perovskite material, Ca_{2/3}Ce_{1/3}Ti_{1/3}Mn_{2/3}O₃, which exhibits high hydrogen production capacity and stable redox performance. The authors identified that the A-site Ce4+ reduction is the key to its enhanced water splitting capabilities. 43 Tran et al. reviewed the potential of perovskite oxides as redox materials for CO2 splitting using solar thermochemical methods. This work highlights their lower reduction temperatures, tunable properties, and challenges such as sintering and cycle stability for solardriven fuel production.44 The other category of redox cycles uses chemical reduction for the oxygen carrier. We refer to review articles and book in this area. 45-47

Building on the previous work, we present chemical looping ammonia oxidation and decomposition integrated with water

Paper

splitting (CLAOD-WS), a novel two-step cyclic process involving redox looping and catalytic reactions for H_2 production from NH_3 and H_2O (Fig. 1b). Here NH_3 is first partially oxidized by a solid oxygen carrier and meanwhile decomposed by a catalyst, to produce H_2 , N_2 , and H_2O (eqn (1)); secondly, H_2O re-oxidizes the oxygen carrier to produce H_2 (eqn (2)).

$$NH_3 + MO_x \rightarrow \left(\frac{3}{2} - \delta\right)H_2 + \frac{1}{2}N_2 + \delta H_2O + MO_{x-\delta}$$
 (1)

$$\delta H_2O + MO_{x-\delta} \rightarrow \delta H_2 + MO_x$$
 (2)

Over CLAOD-WS cycles, the net reaction is the same as NH₃ decomposition producing N2 and H2, but looping presents advantages that will translate to significant energy and cost savings shown by this paper. Firstly, it gives two H2 streams at different purity levels suitable for different applications. On the one hand, the H2 produced by water splitting step is intrinsically separated from N2 and NH3. This H2 has only unreacted H₂O as impurity and is thus more suitable for high-purity H₂ applications such as fuel cells. 48-50 If necessary, this stream of H₂ mixed with unreacted H₂O can be further purified by removing H₂O, which is simpler than H₂ separation from N₂ and unreacted NH₃ in direct NH₃ decomposition. On the other hand, the low-purity H₂ from the NH₃ conversion step is mixed with N2, H2O, and unreacted NH3, and can be suitable for industrial heating and power generation. Secondly, according to Le Chatelier's principle, chemical looping facilitates NH3 conversion thanks to the removal of H2 by the chemical reduction of the oxygen carrier.

Previous literature on system energy and technoeconomic assessments provides information for our analysis of CLAOD-WS in comparison to direct NH3 decomposition in terms of energy consumption, H2 production, and process costs. Yun et al. analyzed catalytic NH3 decomposition plants equipped with various types of H2 separation systems including pressure swing absorption (PSA) and Pd membranes, where the levelized cost of H2 (LCOH) was reported between \$5-7.5 per kg-H₂.⁵¹ Nordio et al. proposed a H₂ separation system integrated with multiple membrane modules and conducted a comprehensive technoeonomic analysis. This study concluded that LCOH ranges between €3.56 and €12.63 per kg-H₂.⁵² Makhloufi et al. studied a large-scale NH₃ cracking system for clean H2 production. This plant showed 68.5% thermal efficiency and €4.83 per kg-H₂.⁵³ In another study by Devkota et al., technoeconomic and environmental assessment of an NH3 decomposition plant equipped with a packed bed reactor concluded that LCOH was \$6.05 per kg-H₂.⁵⁴

This study leverages catalytic and redox activities of FeO_x/YSZ and $Fe_{0.5}Co_{0.5}O_x/YSZ$ for CLAOD-WS. We identified the different redox and catalytic properties of Fe and Co. Also, we showed that kinetic limitation and thermodynamic limitation occurred for different materials under different reaction conditions. Stable 50-cycle operation at 600 °C showed the materials' durability. Our energy and technoeconomic analyses compared CLAOD-WS with direct catalytic NH_3 decomposition systems.

2. Materials and methods

2.1. YSZ supported materials synthesis

Iron oxide and mixed iron-cobalt oxide were synthesized using a modified wet impregnation method. For the iron oxide, Fe(NO₃)₃·9H₂O (Sigma-Aldrich) was mixed with ethanol, and 8% yttria-stabilized zirconia (YSZ8%) ($(ZrO_2)_{0.92}(Y_2O_3)_{0.08}$) (Inframat Advanced Materials) was supplemented to the mixture as the oxygen carrier's support material. The mass of the support material was calculated to be 30% of the total mass of metal oxide and support. The mixture was stirred on a hotplate at 300 rpm for three hours at ambient temperature, followed by heating to 100 °C and stirring for two more hours. At this point, a thick paste was formed which was moved to a box furnace (MTI KSL-1200X) and dried at 200 °C for seven hours (heating and cooling ramp rates were 5 °C min⁻¹). The resulting dry material was ground with a mortar and pestle to obtain a fine powder. Lastly, calcination was carried out under air at 600 °C for three hours (heating and cooling ramp rates were 15 and 5 °C min⁻¹ respectively) in the box furnace. The final product was further ground by mortar and pestle. This sample is denoted as FeOx/YSZ. For the mixed iron-cobalt oxide, Fe(NO₃)₃·9H₂O and Co(NO₃)₂·6H₂O (Sigma-Aldrich) were mixed with the support following the same procedure. This sample is denoted as Fe_{0.5}Co_{0.5}O_x/YSZ.

2.2. Materials looping performance testing

CLAOD-WS experiments were conducted in a U-shaped quartz tube (O.D. = 0.5 in) in a Micromeritics tube furnace. 0.01 g material was uniformly placed inside the tube between quartz wool to form a fixed bed reactor. The reactor was programmed for isothermal reaction temperatures of 450, 500, 550, and 600 °C, with a 15 °C min⁻¹ ramp rate, and three different space velocity values of 6, 18, and 30 L_{NH_2} (g_{solid} h)⁻¹. During heating up, 100 sccm of argon (Ar) flowed over the sample. At the determined reaction temperature, the first step began by flowing NH₃ gas balanced with Ar for 12 minutes unless otherwise noted, and consequently, H₂, N₂, and H₂O were produced. Different concentrations of NH₃ (1%, 3%, and 5%) were chosen for space velocities of 6, 18, and 30 $L_{NH_{*}}$ (g_{solid} h)⁻¹, respectively (eqn (S1)†). In the second step, 2% H₂O vapor diluted in Ar flowed over the reduced material for 3 minutes unless otherwise noted; H₂O step space velocity was equal to 12 $L_{H,O}$ $(g_{solid} h)^{-1}$ in all experiments (eqn (S2)†). After each step, 100 sccm of Ar flowed for 5 minutes to purge the reactor and gas lines. A mass spectrometer (Hiden Analytical HPR-20 R&D) and gas chromatograph (Inficon Micro GC Fusion) were used in parallel to detect and quantify the gas mixture in the exhaust line. Potential NOx was detected at a small amount in the NH₃ step of the first CLAOD-WS cycle for several samples, and no NO_x was detected beyond the first cycle (Fig. S4†).

2.3. Material characterization using XRD

X-ray diffraction (XRD) characterizations were performed using a Rigaku SmartLab X-ray diffractometer at ambient pressure and temperature. The data collection range was 2θ from 20° to 90°

Green Chemistry Paper

with a 0.02° step size and 1.3° min⁻¹ rate. XRD measurements were conducted on NH3-reduced and steam-oxidized samples. To prepare the NH₃-reduced samples, 0.07 g material was reduced by NH₃ gas for 60 minutes and was carefully protected in a glove box filled with Ar due to their sensitivity to air. To prepare the steamoxidized samples, the material was first reduced by NH₃ for 60 minutes and then re-oxidized by H₂O for 30 minutes and protected in Ar glove box. To keep the sample shielded from air oxidation, Kapton tape was used to protect the samples when taking the sample from the glove box to diffractometer.

We used 0.07 g sample for XRD and XANES measurements rather than the 0.01 g used for looping performance experiments because 0.01 g sample gave too low signal-to-noise ratio in the characterization results. Also, the 60-minute duration of the reduction step gave stable concentrations of products (N2 and H₂) for at least 10 minutes in the NH₃ step, meaning the reduction of oxygen carrier was completed and the gas products were exclusively from NH3 decomposition. Similarly, the 30-minute duration of the re-oxidation step gave zero H₂ product concentration for at least 10 minutes so that steam oxidation of the oxygen carrier was completed.

Refinement and Reference Intensity Ratio (RIR) methods in PDXL software were used to analyze the XRD data to quantify the phase compositions. Using chemical stoichiometry and molar mass of different solid phases, the molar ratio of oxygen to Fe plus Co can be calculated for each material at reduced and re-oxidized states. The difference in this ratio between reduced and re-oxidized samples shows the sample's oxygen exchange capacity normalized by the redox active metals (Fe and Co) molar amount (eqn (3)).

$$\Delta\left(\frac{\text{mol O}}{\text{mol M}}\right) = \left(\frac{\text{mol O}}{\text{mol M}}\right)_{\text{oxidized}} - \left(\frac{\text{mol O}}{\text{mol M}}\right)_{\text{reduced}} \tag{3}$$

2.4. Material characterization using XANES

X-ray absorption near edge structure (XANES) was conducted by easyXAFS300+ to measure the change in the oxidation state of the Fe and Co. The X-ray source was set at 36 kV and 20 mA to acquire energy absorption spectra ranging from 7000 eV to 7600 eV for Fe K edge and from 7600 eV to 7900 eV for Co K edge. NH3-reduced and steam-oxidized samples (FeOx/YSZ and Fe_{0.5}Co_{0.5}O_x/YSZ) and standard materials (Co, CoO, Co₃O₄, Fe, Fe₃O₄, and CoFe₂O₄) were protected against air oxidation using Kapton tape. FeO_x/YSZ and Fe_{0.5}Co_{0.5}O_x/YSZ samples were prepared in the same way as XRD samples. X-ray energy value at 0.5 normalized absorption was defined as the edge energy, and the edge energy of the reduced and re-oxidized samples relative to standard materials allowed us to determine the average oxidation states of Fe and Co in our samples. XANES data was analyzed by Athena software to give normalized absorption (μ) vs. absorption energy.⁵⁵

2.5. Material characterization using SEM

Scanning Electron Microscopy (SEM) images were acquired using the Everhart-Thornley Detector (ETD) of a Thermo

Fisher Scientific Apreo Scanning Electron Microscope set at 5 kV and 3.2 nA in the Secondary Electron (SE) mode. As-synthesized or cycled FeOx/YSZ and Fe0.5Co0.5Ox/YSZ were mixed in deionized water and sonicated at ambient temperature (25 °C) for 5 minutes, a 10 µL droplet of the mixture was placed on an SEM stub covered with carbon tape; afterwards, the stub was dried for 5 hours at 80 °C on a hot plate to remove water.

3. Results and discussion

We conducted five-cycle CLAOD-WS experiments using 0.01 g FeO_x/YSZ or $Fe_{0.5}Co_{0.5}O_x/YSZ$ at 450, 500, 550, and 600 °C. Fig. 2a shows reactor outlet gas mixture profile during a 600 °C experiment using FeO_x/YSZ at 6 L_{NH} , $(g_{solid} h)^{-1}$. Initially, NH₃ was mostly oxidized into H₂O, and then when oxygen carrier capacity was used up, NH3 was only catalytically

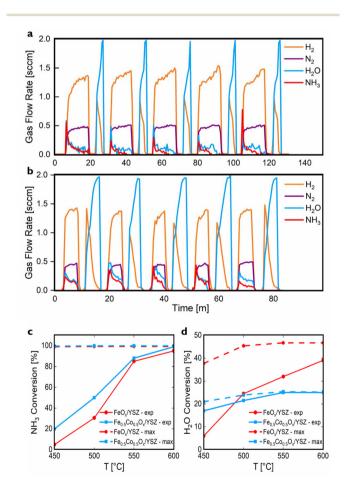


Fig. 2 CLAOD-WS performance for different materials at different temperatures. Reactor outlet gas profiles using FeOx/YSZ at 600 °C with different step durations of (a) $\Delta t_{\rm NH_3}$ = 12 min and $\Delta t_{\rm H_2O}$ = 3 min, and (b) $\Delta t_{\mathrm{NH_3}}$ = 5 min and $\Delta t_{\mathrm{H_2O}}$ = 5 min. (c) NH₃ and (d) H₂O conversions dependence on temperature for Fe_{0.5}Co_{0.5}O_x/YSZ and FeO_x/YSZ. "max" refers to equilibrium and "exp" refers to average over five-cycle CLAOD-WS experiments. Experiments in (a-d) had space velocities 6 L_{NH_3} (g_{solid} h)⁻¹ and 12 L_{H_2O} (g_{solid} h)⁻¹.

decomposed to H_2 and N_2 . In water splitting, H_2O re-oxidizes the oxygen carrier to produce additional H_2 until the re-oxidation is complete.

Space velocities and step durations can be adjusted to regulate the relative ratio of H_2 produced from the two steps. As in Fig. 2a, the ratio of H_2 from the NH_3 and H_2O steps was 7.43:1, while in Fig. 2b with shorter NH_3 step and longer H_2O step, this ratio became 2.13:1. Future research can involve materials chemistry adjustments and process optimizations to enhance high-purity H_2 production from H_2O in the CLAOD-WS system. Also, increasing the space velocity of the NH_3 step from 6 to 30 L_{NH_3} (g_{solid} h) $^{-1}$ only led to minor decay in NH_3 conversion from 99% to 95% for $Fe_{0.5}Co_{0.5}O_x/YSZ$ and from 95% to 84% for FeO_x/YSZ at 600 °C (Fig. S1 and S2†). Therefore, sufficiently high conversions were achieved at space velocities suitable for commercial use conditions (≥ 7.8 L_{NH_3} (g_{solid} h) $^{-1}$). 56

Experimental results from different temperatures are demonstrated in Fig. 2c, d, S1, and S2.† The solid lines indicate experimental results in Fig. 2c and d, while the dashed lines show thermodynamic equilibrium simulation results via FactSage software, giving the maximum possible conversions of NH $_3$ and H $_2$ O. Fig. 2c shows an increasing trend in experimental NH $_3$ conversion as the temperature increases due to kinetics enhancement. Meanwhile, water splitting is improved at higher temperatures (Fig. 2d), specifically in FeO $_x$ /YSZ, because both reaction kinetics and equilibrium H $_2$ O conversion are improved at elevated temperatures.

To measure the materials' durability, 50-cycle CLAOD-WS were conducted at 600 °C and 30 $L_{\rm NH_3}$ ($g_{\rm solid}$ h)⁻¹ space velocity, the most demanding reaction condition in this paper. Over the 50 cycles, FeO_x/YSZ had only slight decays of 1.3% and 0.9% in NH₃ and H₂O conversions, respectively (Fig. 3a). Similarly, in Fig. 3d, Fe_{0.5}Co_{0.5}O_x/YSZ gave slight decays of 1.6% and 0.6% in NH₃ and H₂O conversions, respectively. Scanning electron microscope (SEM), showed surface topology and particle size did not change after the 50-cycle experiments (Fig. 3b–f), indicating negligible agglomeration and sintering. Stability assessment of these materials in commercial reactors requires longer duration which is out of the scope of this study.

Fig. 3g compares H_2 yield from NH_3 between chemical looping (only counting H_2 from the NH_3 step) and catalytic NH_3 decomposition in literature. The looping scheme shows high H_2 yields from the NH_3 at a range of space velocities. Fig. 3h compares thermochemical water splitting in literature with our CLAOD-WS experiments in millimoles H_2 production from H_2O per gram of oxygen carrier (OC). FeO_x/YSZ and Fe_{0.5}Co_{0.5}O_x/YSZ are among the best-performing water splitting oxygen carriers.

Other oxygen carriers and catalysts FeO_x/Al_2O_3 , $Fe_{0.5}Co_{0.5}O_x/Al_2O_3$, CoO_x/YSZ , NiO_x/YSZ , and $Fe_{0.5}Ni_{0.5}O_x/YSZ$ were also synthesized and tested for CLAOD-WS (Fig. S3 and Table S1†). We found that Al_2O_3 is not as effective a support as YSZ. Also, Co and Ni both showed minimal water splitting performance due to limited redox capacity. Additionally, Co is a better NH_3 conversion catalyst than Ni.

Material solid-phase transformation was studied by X-ray diffraction. At 450 °C, Fe_{0.5}Co_{0.5}O_x/YSZ was fully reduced by NH₃ to iron-cobalt metallic alloy (Fig. 4a), and then oxidized by H₂O to spinel phase while a portion of Co remained metallic (Fig. 4b), so the steam oxidation limited the redox capacity. With the same reaction conditions, FeO_y/YSZ was partially reduced by NH3 to metallic iron with a spinel oxide phase remaining (Fig. 4c), and then oxidized by H₂O to complete spinel (Fig. 4d), so the reduction reaction limited the redox capacity. At 600 °C, FeOx/YSZ was fully reduced by NH3 to metallic Fe (Fig. 4g); and then fully oxidized by H2O to spinel (Fig. 4h), giving complete phase transformation and thus high redox capacity. However, the Fe_{0.5}Co_{0.5}O_x/YSZ exhibited full reduction to metallic phase but still partial oxidation to spinel phase at 600 °C (Fig. 4e and f), similar to its behavior at 450 °C. Therefore, the elevated temperature more significantly enhanced the redox phase transformation of FeOx/YSZ than Fe_{0.5}Co_{0.5}O_x/YSZ, explaining their looping performance trend in Fig. 2d. Kapton tape was used to minimize XRD samples' oxidation by air, so amorphous peaks at 2θ of 20° to 30° showed up.

The red arrows in Fig. 4i and j indicate the phase transition range at equilibrium conditions of NH $_3$ reduction and H $_2$ O reoxidation steps. For Fe–O system, at lower temperatures, the equilibrium phase transition is directly from Fe to Fe $_3$ O $_4$, whereas at 600 °C the phase transition becomes Fe \rightarrow FeO \rightarrow Fe $_3$ O $_4$. Fig. 4c showed that FeO $_x$ /YSZ was not fully reduced by NH $_3$ to the metallic phase at 450 °C. Therefore, kinetic limitation prevented FeO $_x$ /YSZ from achieving a fully reduced state at 450 °C. For the Fe–Co–O system, after oxidation at both temperatures, a portion of Co remains in the metallic phase due to thermodynamic limitation, consistent with XRD results. Therefore, thermodynamic limitation prevents metallic Co from being completely oxidized by H $_2$ O and thus limits the redox capacity of Fe $_0.5$ Co $_0.5$ O $_x$ /YSZ compared to FeO $_x$ /YSZ.

By XRD refinement, the oxygen-to-metal molar ratios were calculated for 450 °C and 600 °C looping, and are shown in Fig. 4k. At 450 °C, owing to the full reduction of $Fe_{0.5}Co_{0.5}O_x/YSZ$ and its oxidation to mostly spinel phase, the redox capacity of $Fe_{0.5}Co_{0.5}O_x/YSZ$ is significantly higher than that of FeO_x/YSZ . At 600 °C, full reduction of FeO_x/YSZ to metallic phase followed by full oxidation to spinel phase resulted in its higher oxygen capacity than $Fe_{0.5}Co_{0.5}O_x/YSZ$. These are consistent with their water splitting capacity performance (Fig. 2d). The redox capacity of $Fe_{0.5}Co_{0.5}O_x/YSZ$ is not significantly different between 450 °C and 600 °C based on XRD refinement, so X-ray Absorption Near Edge Structure (XANES) was utilized to further interpret each element's redox behavior.

XANES was conducted to analyze oxidation states of Fe and Co. Fig. 5a and b demonstrate Co K edge XANES spectra of NH₃-reduced and steam-oxidized Fe_{0.5}Co_{0.5}O_x/YSZ at 450 °C and 600 °C, along with standard materials Co, CoO, and Co₃O₄. Comparing the edge energy shifts at the normalized absorption of 0.5 gave that at 450 °C, Co underwent an oxidation state variation of 1.49; whereas at 600 °C, Co underwent a much lower oxidation state change of 0.71, proving that Co

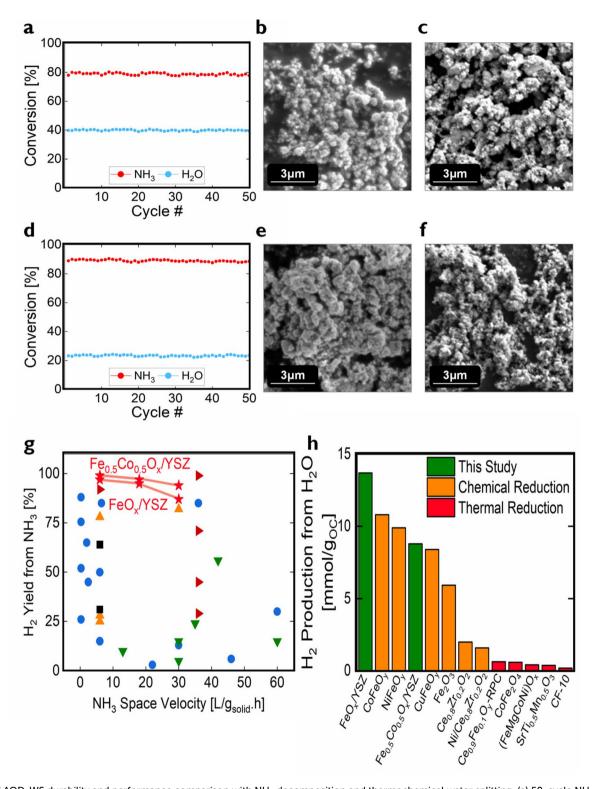


Fig. 3 CLAOD-WS durability and performance comparison with NH₃ decomposition and thermochemical water splitting. (a) 50-cycle NH₃ and H₂O conversions using FeO_x/YSZ at 600 °C, with 30 L_{NH_3} (g_{solid} h)⁻¹ for 12 min, 12 L_{H_2O} (g_{solid} h)⁻¹ for 3 min. SEM images of (b) as-synthesized FeO_x/YSZ, and (c) 50-cycled FeO_x/YSZ. (d-f) are Fe_{0.5}Co_{0.5}O_x/YSZ results corresponding to (a-c). (g) H₂ yield from NH₃ in our 600 °C CLAOD-WS experiments (red star, only counting H₂ from the NH₃ step), compared to direct decomposition catalysts in literature ranging 450 °C to 700 °C (blue circle: Febased, ^{23,57–69} black square: Co-based, ^{66,70,71} orange triangle: Ni-based, ^{72,73} brown triangle: mixed transition metals, ^{21,22} green triangle: noble metalbased^{74–77}). (h) H_2 production in our 600 °C CLAOD-WS experiments (green, only counting H_2 from the H_2 O step), compared to thermochemical water splitting in literature (orange: chemical reduction ranging 650 °C to 900 °C, ^{36,78,79} red: thermal reduction ^{28–30,33,37,80–82}).

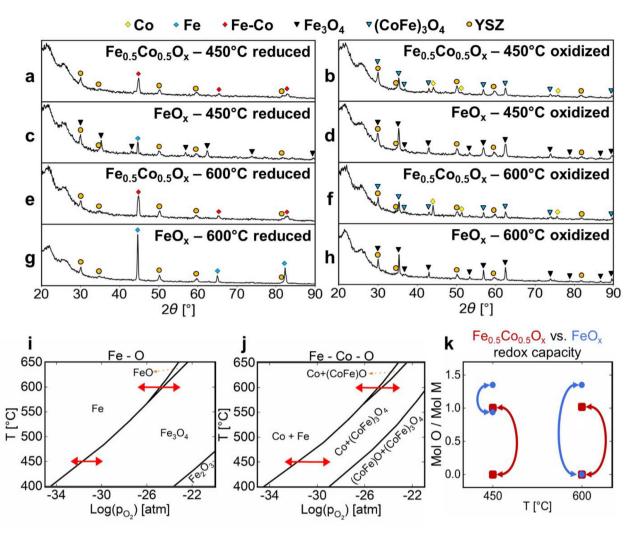


Fig. 4 Solid-state phase transformation of materials for CLAOD-WS. XRD patterns of NH₃-reduced and steam-oxidized samples: (a) reduced $Fe_{0.5}Co_{0.5}O_x/YSZ$, (b) re-oxidized $Fe_{0.5}Co_{0.5}O_x/YSZ$, (c) reduced $Fe_{0.5}Co_{0.5}O_x/YSZ$, and (d) re-oxidized $Fe_{0.5}Co_{0.5}O_x/YSZ$ at 450 °C; (e-h) are results at 600 °C corresponding to (a-d). (i) $Fe_{0.5}Co_{0.5}O_x/YSZ$, and (j) $Fe_{0.5}Co_{0.5}O_x/YSZ$, where red arrows indicate the equilibrium $Fe_{0.5}Co_{0.5}O_x/YSZ$ (red) at 450 °C and 600 °C, concluded from XRD refinement.

becomes less redox active at the higher temperature of 600 °C. Fig. 5c and d show the Fe edge XANES results of reduced and re-oxidized Fe_{0.5}Co_{0.5}O_x/YSZ along with standard materials of Fe, Fe₃O₄, and CoFe₂O₄. We found that at 450 °C Fe underwent a smaller oxidation state variation than at 600 °C. The oxidation state changes of Co and Fe (Tables S2, S3, and S4, and Fig. S6†) were then weight-averaged based on their mole fractions to result in the overall metal redox capacity of Fe_{0.5}Co_{0.5}O_x/YSZ at 450 °C and 600 °C in Table 1. Additionally, Fig. 5e and f show the Fe redox of FeO_x/YSZ. The order of overall oxidation state variation in Table 1 agreed with those of water splitting capacity (Fig. 2d) and oxygen capacity derived from XRD phase transformation (Fig. 4k). At 450 °C, Fe_{0.5}Co_{0.5}O_x/YSZ is a more redox-active material, while at 600 °C FeO_x/YSZ becomes more redox-active.

As discussed earlier, the materials for CLAOD-WS play the dual-role of oxygen carriers and catalysts. XRD and XANES

characterizations of NH3-reduced and H2O-oxidized samples illustrate their catalytic activity. For 600 °C experiments, XRD results in Fig. 4e and g show that the FeOx/YSZ and $Fe_{0.5}Co_{0.5}O_x/YSZ$ are fully reduced in NH₃ step to metal phases of Fe and Fe-Co alloy, while the support material YSZ remained unchanged in crystal structure. The XANES experiments (Fig. 5b, d, and f) also show the fully reduced metal phases. Combining the results of XRD and XANES, the metal phases are the active sites for NH3 decomposition that continues beyond the NH3 oxidation reaction. High conversions of NH₃ at 600 °C (99% for Fe_{0.5}Co_{0.5}O_x/YSZ and 95% for FeO_x/ YSZ) show that metal phases are highly catalytically active for NH₃ decomposition at 600 °C. Additionally, we tested as-synthesized and H2-reduced samples for NH3 conversion and observed that H₂-reduced samples reach their maximum NH₃ conversion faster than as-synthesized oxides (Fig. S5†), indicating that after reduction of oxides to metal phases, NH₃ conver-

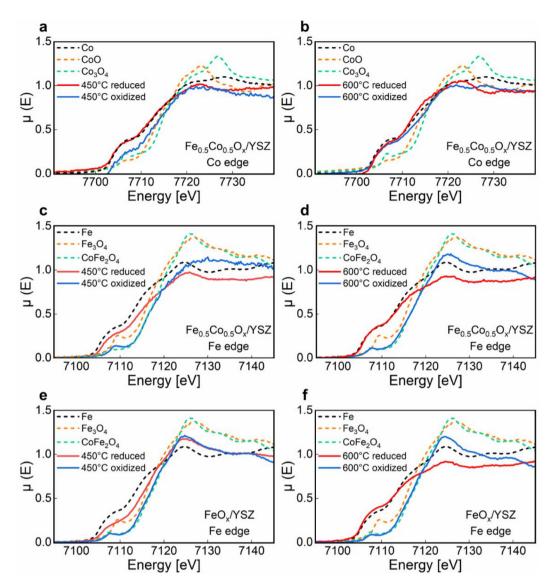


Fig. 5 Simultaneous redox reactions of Fe and Co for CLAOD-WS. XANES results for Co and Fe between NH₃-reduced and steam-oxidized states: Co K edge of Fe_{0.5}Co_{0.5}O_x/YSZ at (a) 450 °C and (b) 600 °C, Fe K edge of Fe_{0.5}Co_{0.5}O_x/YSZ at (c) 450 °C and (d) 600 °C, and Fe K edge of FeO_x/YSZ at (e) 450 °C and (f) 600 °C.

 $\begin{tabular}{ll} \textbf{Table 1} & \textbf{Change in the overall oxidation state of active metals according to XANES} \end{tabular}$

<i>T</i> [°C]	Overall averaged oxidation state variation per mol of active metals (Fe & Co)	
	FeO _x /YSZ	Fe _{0.5} Co _{0.5} O _x /YSZ
450 600	1.31 2.86	1.59 1.86

sion is significantly enhanced due to catalytic activity of these active metal sites.

In comparison, at 450 °C, Fig. 4a shows that $Fe_{0.5}Co_{0.5}O_x/YSZ$ is fully reduced to Fe–Co metal phase and this phase is

responsible for catalytic NH $_3$ decomposition; however, due to the lower temperature at 450 °C, NH $_3$ conversion is relatively low (20%). Fig. 4c shows that FeO $_x$ /YSZ is partly reduced to metal Fe phase mixed with Fe $_3$ O $_4$ spinel phase, resulting in a significantly lower NH $_3$ conversion of 5% at 450 °C. The XANES experiments for 450 °C samples also agreed with the XRD results. For FeO $_x$ /YSZ, Fig. 5e showed that the oxidation state of Fe is very close to that of Fe $_3$ O $_4$. For Fe $_{0.5}$ Co $_{0.5}$ O $_x$ /YSZ sample, Fig. 5a (Co edge) and Fig. 5c (Fe edge) show that Co and Fe are both reduced to metal phases which are the active phases for NH $_3$ conversion.

Energy and techno-economic analyses were conducted to assess two systems: (1) Chemical looping ammonia oxidation and decomposition integrated with water splitting (CLAOD-WS) (Fig. 6a), and (2) Catalytic ammonia decompo-

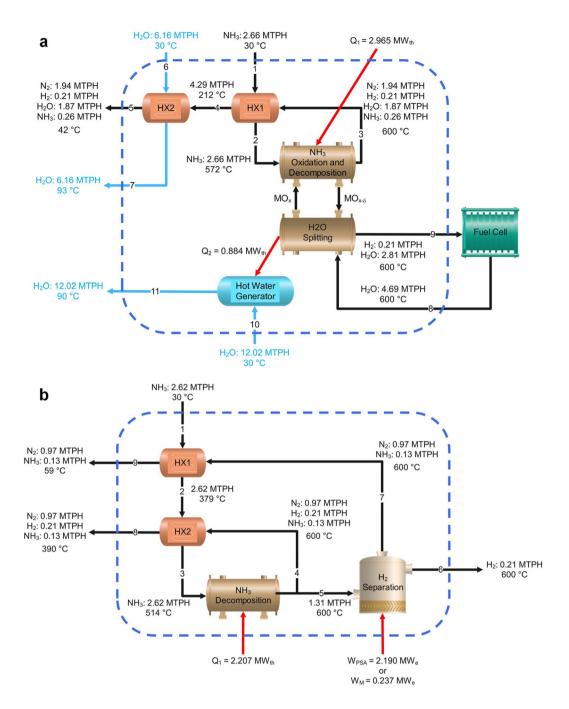


Fig. 6 Process schematics with major model parameters of (a) chemical looping ammonia oxidation and decomposition integrated with water splitting (CLAOD-WS), and (b) catalytic ammonia decomposition (CAD). MTPH: metric ton per hour.

sition (CAD) (Fig. 6b). Major assumptions for both scenarios are: NH₃ conversion is 90%, steam conversion is 40%, reaction temperature is 600 °C, total pressure is 1 atm (except for the PSA where the compressor increases the pressure to 700 kPa), heat exchanger effectiveness is 95%, total H₂ production rate is 10 metric tons per day, and electricity serves as the energy input and is converted to heat when needed and the cost of electricity is assumed to be \$0.053 per kWh_e (following utility-

scale PV-plus-battery system, class 5, moderate case, market, PTC + ITC, 2030). For CLAOD-WS, 5 tons per day of H₂ comes out of each of NH₃ reaction and steam reaction. For CAD, 5 tons per day of H₂ is purified in the separation step, where two types of H₂ separation technologies were analyzed: PSA and Pd-Ag membrane supported on ceramic material. Base case membrane separation has a Second Law efficiency of 20%. The redox or catalyst material is assumed to be replaced 4 times

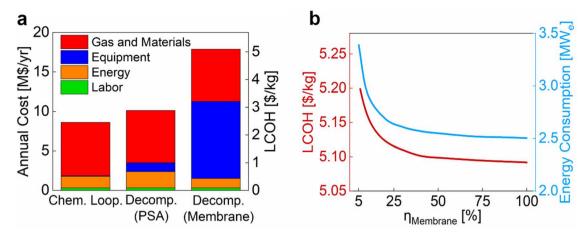


Fig. 7 (a) Annual cost and levelized cost of hydrogen (LCOH) for CLAOD-WS and for CAD equipped with pressure swing absorption (PSA) or Pd-Ag/ceramic membrane separation. (b) Dependence of LCOH and total system energy consumption rate on H₂ separation membrane Second Law efficiency in CAD process with Pd-Ag/ceramic membrane separation.

per year, ⁸⁴ and we find that the replacement frequency varying from once per year to once per two weeks only changes LCOH by less than 2% for all cases in this work.

In CLAOD-WS, the NH_3 step is the main thermal energy consumer (2.965 $\mathrm{MW}_{\mathrm{th}}$). In CAD, although the chemical reactor is less energy intensive (2.207 $\mathrm{MW}_{\mathrm{th}}$), the H_2 separation requires an energy input of 0.237 MW_{e} for the membrane and 2.190 MW_{e} for the PSA. Overall, the CLAOD-WS system is 22.5% more energy-consuming than the membrane-based CAD system and 29.1% less energy-consuming than the PSA-based CAD system.

As Fig. 7a shows, notably, CLAOD-WS process achieves cost savings of 52% and 86% in energy and equipment expenses compared to CAD plants utilizing PSA and membrane systems, respectively. The CLAOD-WS plant requires an annual cost of \$8.64 M, 51.8% lower than the CAD plant equipped with membrane separation and 14.8% lower than the CAD plant equipped with PSA separation. Accordingly, the LCOH is \$2.5 per kg-H₂ in CLAOD-WS, \$5.1 per kg-H₂ in CAD with membrane, and \$2.9 per kg-H₂ in CAD with PSA. LCOH refers to the cost per kilogram of H₂ production from both NH₃ and H₂O steps in CLAOD-WS. In addition, thermal energy release in CLAOD-WS can be used to produce hot water byproduct, whose revenue is not included in our economic analysis. Fig. 7b compares the LCOH and total energy consumption rate in the CAD as a function of the membrane's H2 separation Second Law efficiency, showing the impact of membrane performance.

4. Conclusions

We have proposed and studied integrated chemical looping NH_3 oxidation and decomposition with water splitting (CLAOD-WS) as a promising novel pathway toward H_2 production from NH_3 and H_2O . FeO_x/YSZ and $Fe_{0.5}Co_{0.5}O_x/YSZ$ each played the dual roles of oxygen carrier and catalyst.

Looping experiments at 450 to 600 °C and space velocities of 6, 18, and 30 $L_{NH_3} (g_{solid} h)^{-1}$ and 12 $L_{H_2O} (g_{solid} h)^{-1}$ were conducted. XRD coupled with phase diagrams illustrated that FeOx/YSZ is kinetically limited from achieving full reduction at 450 °C, while Fe_{0.5}Co_{0.5}O_x/YSZ is thermodynamically limited from complete oxidation under H2O. Moreover, XRD refinements and XANES results showed the Fe and Co redox activities that explain the overall redox capacity of Fe_{0.5}Co_{0.5}O_x/YSZ and FeOx/YSZ at different temperatures, consistent with the experimental water splitting capacity. Durability of the materials was shown by 50-cycle CLAOD-WS experiments at 600 °C and 30 L_{NH_2} (g_{solid} h)⁻¹. Lastly, energy and techno-economic analysis of the CLAOD-WS and catalytic NH3 decomposition systems indicated that the looping scheme can significantly reduce energy consumption and cost mainly due to the intrinsic H₂ purification in the looping scheme.

Data availability

Further information on materials and code used in the work are available from the lead contact upon reasonable request. Crystallographic data used for XRD data analysis has been deposited at the ICSD and can be obtained from https://icsd.products.fiz-karlsruhe.de/en. Additional data used in this study is available in the ESI.†

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

The authors acknowledge Center for Electron Microscopy and Analysis (CEMAS) and Surface Analysis Laboratory at The Ohio State University (OSU). The research is partly supported by OSU President's Research Excellence Program. A. Arjomand is partly supported by US Department of Energy DE-EE0010733. K. Shank is supported by Distinguished University Fellowship and ENGIE-Axium Fellowship at OSU.

References

Paper

- S. Ristig, M. Poschmann, J. Folke, O. Gómez-Cápiro,
 Z. Chen, N. Sanchez-Bastardo, R. Schlögl, S. Heumann and
 H. Ruland, *Chem. Ing. Tech.*, 2022, 94, 1413–1425.
- 2 B. Modu, M. P. Abdullah, A. L. Bukar and M. F. Hamza, *Int. J. Hydrogen Energy*, 2023, **48**, 38354–38373.
- 3 A. Arjomand Kermani and E. Houshfar, *Int. J. Hydrogen Energy*, 2024, 52, 177–189.
- 4 I. Lucentini, X. Garcia, X. Vendrell and J. Llorca, *Ind. Eng. Chem. Res.*, 2021, 18560–18611.
- 5 A. Pal, S. Kakran, A. Kumar, A. B. Youssef, U. P. Singh and A. Sidhu, *Int. J. Hydrogen Energy*, 2024, 49, 16–41.
- 6 M. Koleva and N. Rustagi, Hydrogen Delivery and Dispensing Cost - DOE Hydrogen and Fuel Cells Program Record.
- 7 J. W. Sheffield, K. B. Martin and R. Folkson, in *Alternative Fuels and Advanced Vehicle Technologies for Improved Environmental Performance*, ed. R. Folkson, Woodhead Publishing, 2014, pp. 117–137.
- 8 Physical Hydrogen Storage Hydrogen and Fuel Cell Technologies Office, https://energy.gov/eere/fuelcells/physical-hydrogen-storage.
- 9 L. Mulky, S. Srivastava, T. Lakshmi, E. R. Sandadi, S. Gour, N. A. Thomas, S. Shanmuga Priya and K. Sudhakar, *Mater. Chem. Phys.*, 2024, 325, 129710.
- 10 F. Dawood, M. Anda and G. M. Shafiullah, *Int. J. Hydrogen Energy*, 2020, 45, 3847–3869.
- 11 M. F. Platzer and N. Sarigul-Klijn, in *The Green Energy Ship Concept: Renewable Energy from Wind Over Water*, ed. M. F. Platzer and N. Sarigul-Klijn, Springer International Publishing, Cham, 2021, pp. 71–72.
- 12 A. Valera-Medina, H. Xiao, M. Owen-Jones, W. I. F. David and P. J. Bowen, *Prog. Energy Combust. Sci.*, 2018, **69**, 63–102.
- 13 A. Roy, S. Sen Gupta, A. Samanta, P. V. S. Sai Likhith and S. K. Das, *Int. J. Hydrogen Energy*, 2024, 71, 131–142.
- 14 N. Othman, H. Salleh and H. Purwanto, *Procedia Chem.*, 2016, 119–124.
- 15 R. Lan, J. T. S. Irvine and S. Tao, *Int. J. Hydrogen Energy*, 2012, 37, 1482–1494.
- 16 J. Bartels, *A Feasibility Study of Implementing an Ammonia Economy*, Iowa State University, 2008.
- 17 L. Zhai, S. Liu and Z. Xiang, *Ind. Chem. Mater.*, 2023, **1**, 332-342.
- 18 O. Ojelade and S. Zaman, *Chem. Pap.*, 2020, 57–65.
- 19 F. Schuth, R. Palkovits, R. Schlogl and D. S. Su, *Energy Environ. Sci.*, 2011, 6278–6289.
- 20 Z. Hu, C. Weng, C. Chen and Z. Yuan, *Appl. Catal., A*, 2018, 49–57.

- 21 H. Tabassum, S. Mukherjee, J. Chen, D. Holiharimanana, S. Karakalos, X. Yang, S. Hwang, T. Zhang, B. Lu, M. Chen, Z. Tang, E. A. Kyriakidou, Q. Ge and G. Wu, *Energy Environ. Sci.*, 2022, 15, 4190–4200.
- 22 P. Xie, Y. Yao, Z. Huang, Z. Liu, J. Zhang, T. Li, G. Wang, R. Shahbazian-Yassar, L. Hu and C. Wang, *Nat. Commun.*, 2019, **10**, 4011.
- 23 Y.-Q. Gu, Z. Jin, H. Zhang, R.-J. Xu, M.-J. Zheng, Y.-M. Guo, Q.-S. Song and C.-J. Jia, *J. Mater. Chem. A*, 2015, 3, 17172– 17180
- 24 L. Yao, T. Shi, Y. Li, J. Zhao, W. Ji and C.-T. Au, *Catal. Today*, 2011, **164**, 112–118.
- 25 F. Normann, A. O. Wismer, C. R. Müller and H. Leion, *Fuel*, 2019, 57–63.
- 26 M. Cheng, F. Normann, D. Zhao, Z. Li, N. Cai and H. Leion, *Energy Fuels*, 2015, 8126–8134.
- 27 C. Ruan, X. Wang, C. Wang, L. Zheng, L. Li, J. Lin, X. Liu, F. Li and X. Wang, *Nat. Commun.*, 2022, 1–12.
- 28 S. Zhai, J. Rojas, N. Ahlborg, K. Lim, M. F. Toney, H. Jin, W. C. Chueh and A. Majumdar, *Energy Environ. Sci.*, 2018, 2172–2178.
- 29 X. Qian, J. He, E. Mastronardo, B. Baldassarri, C. Wolverton and S. M. Haile, *Chem. Mater.*, 2020, 32, 9335–9346.
- 30 Y. Mao, Y. Gao, W. Dong, H. Wu, Z. Song, X. Zhao, J. Sun and W. Wang, *Appl. Energy*, 2020, **267**, 114860.
- 31 A. Pérez, M. Orfila, M. Linares, R. Sanz, J. Marugán, R. Molina and J. A. Botas, *Catal. Today*, 2022, 390–391, 22– 33.
- 32 X. Li, X. Sun, Q. Song, Z. Yang, H. Wang and Y. Duan, *Int. J. Hydrogen Energy*, 2022, 47, 33619–33642.
- 33 C. Bu, T. Gu, S. Cen, D. Liu, J. Meng, C. Liu, X. Wang, H. Xie, J. Zhang and G. Piao, *Int. J. Hydrogen Energy*, 2023, 48, 12227–12239.
- 34 V. K. Budama, J. P. Rincon Duarte, M. Roeb and C. Sattler, *Sol. Energy*, 2023, **249**, 353–366.
- 35 B. Ghorbani, S. Zendehboudi, Y. Zhang, H. Zarrin and I. Chatzis, *Energy Convers. Manage.*, 2023, 297, 117599.
- 36 Y. Liu, T. Gu, C. Bu, D. Liu and G. Piao, *Int. J. Hydrogen Energy*, 2024, **62**, 1077–1088.
- 37 A. M. Huerta-Flores, F. Torre, M. Taeño, R. C. Barreno, E. Palomo Del Barrio and S. Doppiu, *Int. J. Hydrogen Energy*, 2024, 71, 1293–1302.
- 38 J. T. Tran, K. J. Warren, D. Mejic, R. L. Anderson, L. Jones, D. S. Hauschulz, C. Wilson and A. W. Weimer, *Joule*, 2023, 7, 1759–1768.
- 39 E. Gager, M. Frye, D. McCord, J. Scheffe and J. C. Nino, *Int. J. Hydrogen Energy*, 2022, 47, 31152–31164.
- 40 D. Zhang, H. A. De Santiago, B. Xu, C. Liu, J. A. Trindell, W. Li, J. Park, M. A. Rodriguez, E. N. Coker, J. D. Sugar, A. H. McDaniel, S. Lany, L. Ma, Y. Wang, G. Collins, H. Tian, W. Li, Y. Qi, X. Liu and J. Luo, *Chem. Mater.*, 2023, 35, 1901–1915.
- 41 G. L. Schieber, E. B. Stechel, A. Ambrosini, J. E. Miller and P. G. Loutzenhiser, *Int. J. Hydrogen Energy*, 2017, 42, 18785– 18793

- 42 B. Bulfin, M. Miranda and A. Steinfeld, Front. Energy Res., 2021, 9, 677980.
- 43 R. B. Wexler, G. Sai Gautam, R. T. Bell, S. Shulda, N. A. Strange, J. A. Trindell, J. D. Sugar, E. Nygren, S. Sainio, A. H. McDaniel, D. Ginley, E. A. Carter and E. B. Stechel, *Energy Environ. Sci.*, 2023, 16, 2550–2560.
- 44 H. N. N. Tran, W. Li and X. Liu, *Chem. Eng. J.*, 2024, **500**, 156613.
- 45 L.-S. Fan and F. Li, *Ind. Eng. Chem. Res.*, 2010, **49**, 10200–10211.
- 46 L.-S. Fan, *Chemical looping partial oxidation: gasification, reforming, and chemical syntheses*, Cambridge University Press, 2017.
- 47 X. Zhu, Q. Imtiaz, F. Donat, C. R. Müller and F. Li, *Energy Environ. Sci.*, 2020, **13**, 772–804.
- 48 Z. Du, C. Liu, J. Zhai, X. Guo, Y. Xiong, W. Su and G. He, *Catalysts*, 2021, **11**, 393.
- 49 I. Staffell, D. Scamman, A. Velazquez Abad, P. Balcombe, P. E. Dodds, P. Ekins, N. Shah and K. R. Ward, *Energy Environ. Sci.*, 2019, 12, 463–491.
- 50 K. Wróbel, J. Wróbel, W. Tokarz, J. Lach, K. Podsadni and A. Czerwiński, *Energies*, 2022, **15**, 8937.
- 51 S. Yun, J. Im, J. Kim, H. Cho and J. Lee, *Chem. Eng. J.*, 2024, **491**, 151875.
- 52 M. Nordio, S. A. Wassie, M. Van Sint Annaland, D. A. Pacheco Tanaka, J. L. Viviente Sole and F. Gallucci, *Int. J. Hydrogen Energy*, 2021, 46, 23417–23435.
- 53 C. Makhloufi and N. Kezibri, *Int. J. Hydrogen Energy*, 2021, 46, 34777-34787.
- 54 S. Devkota, J.-Y. Cha, B.-J. Shin, J.-H. Mun, H. C. Yoon, S. A. Mazari and J.-H. Moon, *Appl. Energy*, 2024, 358, 122605.
- 55 B. Ravel and M. Newville, *J. Synchrotron Radiat.*, 2005, **12**, 537–541.
- 56 H. F. Rase and J. R. Holmes, *Chemical reactor design for process plants*, Wiley, New York, 1977.
- 57 X. Duan, G. Qian, X. Zhou, Z. Sui, D. Chen and W. Yuan, *Appl. Catal.*, *B*, 2011, **101**, 189–196.
- 58 A.-H. Lu, J.-J. Nitz, M. Comotti, C. Weidenthaler, K. Schlichte, C. W. Lehmann, O. Terasaki and F. Schüth, J. Am. Chem. Soc., 2010, 132, 14152–14162.
- 59 M. Itoh, M. Masuda and K.-I. Machida, *Mater. Trans.*, 2002, 43, 2763–2767.
- 60 T. Otremba, N. Frenzel, M. Lerch, T. Ressler and R. Schomäcker, *Appl. Catal.*, A, 2011, 392, 103–110.
- 61 Z.-P. Hu, L. Chen, C. Chen and Z.-Y. Yuan, Mol. Catal., 2018, 455, 14–22.
- 62 X.-C. Hu, W.-W. Wang, Z. Jin, X. Wang, R. Si and C.-J. Jia, J. Energy Chem., 2019, 38, 41–49.

- 63 H. Tüysüz, F. Schüth, L. Zhi, K. Müllen and M. Comotti, *ChemCatChem*, 2015, 7, 1453–1459.
- 64 B. Lorenzut, T. Montini, M. Bevilacqua and P. Fornasiero, *Appl. Catal.*, *B*, 2012, **125**, 409–417.
- 65 W. Arabczyk and J. Zamlynny, *Catal. Lett.*, 1999, **60**, 167–171.
- 66 H. Zhang, Y. A. Alhamed, Y. Kojima, A. A. Al-Zahrani and L. A. Petrov, *Proceedings of the Bulgarian Academy of Sciences*, 2013, 519–524.
- 67 K. F. Ortega, D. Rein, C. Lüttmann, J. Heese, F. Özcan, M. Heidelmann, J. Folke, K. Kähler, R. Schlögl and M. Behrens, *ChemCatChem*, 2017, 9, 659–671.
- 68 L. Li, Q. Meng, W. Ji, J. Shao, Q. Xu and J. Yan, *Mol. Catal.*, 2017, 442, 147–153.
- 69 Y. Yuan, Science, 2022, 889-893.
- 70 C. Huang, Y. Yu, X. Tang, Z. Liu, J. Zhang, C. Ye, Y. Ye and R. Zhang, *Appl. Surf. Sci.*, 2020, 532, 147335.
- 71 S. Podila, H. Driss, S. F. Zaman, Y. A. Alhamed, A. A. AlZahrani, M. A. Daous and L. A. Petrov, *J. Mol. Catal.* A: Chem., 2016, 414, 130–139.
- 72 K. Okura, K. Miyazaki, H. Muroyama, T. Matsui and K. Eguchi, *RSC Adv.*, 2018, **8**, 32102–32110.
- 73 H. Liu, H. Wang, J. Shen, Y. Sun and Z. Liu, *Appl. Catal.*, *A*, 2008, 337, 138–147.
- 74 S.-F. Yin, B.-Q. Xu, C.-F. Ng and C.-T. Au, *Appl. Catal., B*, 2004, **48**, 237–241.
- 75 P. F. Ng, L. Li, S. Wang, Z. Zhu, G. Lu and Z. Yan, *Environ. Sci. Technol.*, 2007, 3758–3762.
- 76 R. Antunes, R. Steiner, L. Marot and E. Meyer, *Int. J. Hydrogen Energy*, 2022, 47, 14130–14140.
- 77 B. Bahrami, V. G. Komvokis, M. S. Ziebarth, O. S. Alexeev and M. D. Amiridis, *Appl. Catal.*, *B*, 2013, **130–131**, 25–35.
- 78 Y. Qiu, S. Zhang, D. Cui, M. Li, J. Zeng, D. Zeng and R. Xiao, *Appl. Energy*, 2019, **252**, 113454.
- 79 Y. Zheng, K. Li, H. Wang, X. Zhu, Y. Wei, M. Zheng and Y. Wang, *Energy Fuels*, 2016, 30, 638–647.
- 80 K. Zheng, Z. Yu, S.-C. Tan, T. Liu and H. Kong, *Energy Convers. Manage.*, 2024, **303**, 118116.
- 81 A. Haeussler, S. Abanades, A. Julbe, J. Jouannaux, M. Drobek, A. Ayral and B. Cartoixa, *Chem. Eng. Res. Des.*, 2020, **156**, 311–323.
- 82 M. Orfila, D. Sanz, M. Linares, R. Molina, R. Sanz, J. Marugán and J.Á Botas, *Int. J. Hydrogen Energy*, 2021, 46, 17458–17471.
- 83 Annual Technology Baseline Utility Scale PV plus Battery, https://atb.nrel.gov/electricity/2024/utility-scale_pv-plus-battery.
- 84 S. Zhai, Iron-based Oxides for Thermochemical Splitting of Water and Carbon Dioxide, Stanford University, 2020.