


# Nanoscale Advances

Volume 7  
Number 14  
21 July 2025  
Pages 4223–4500

[rsc.li/nanoscale-advances](https://rsc.li/nanoscale-advances)

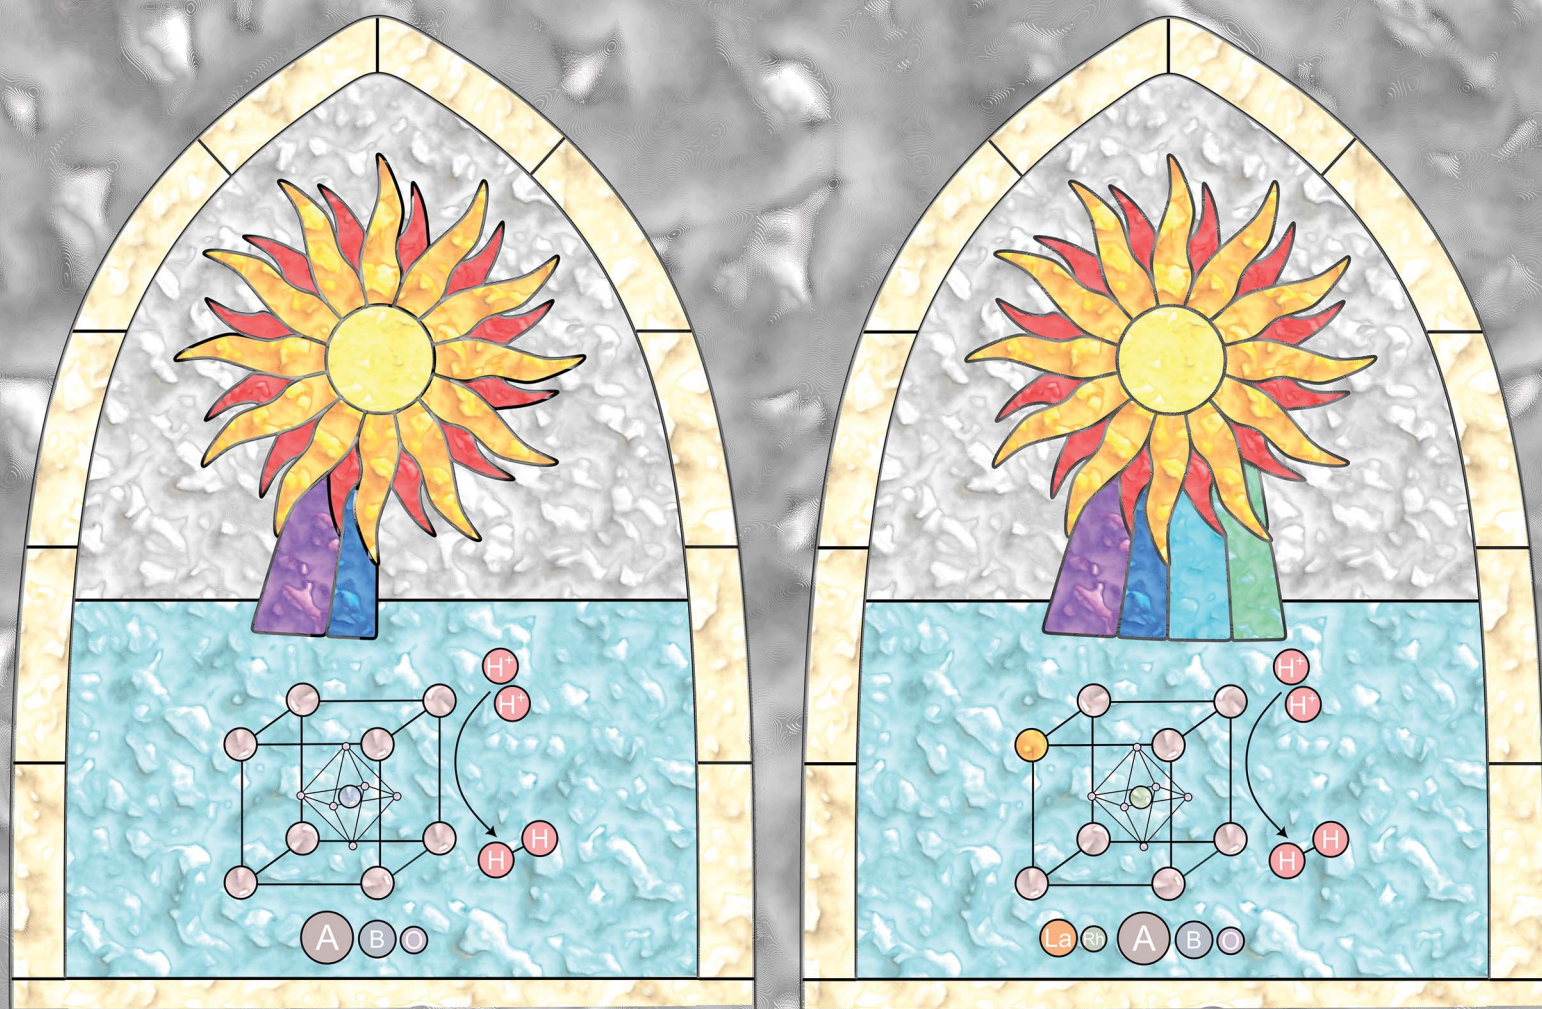

ISSN 2516-0230

## PAPER

Cameron J. Shearer, Gregory F. Metha *et al.*  
Systematic investigation of  $\text{ABO}_3$  perovskite synthesis to  
generalise a La and Rh co-doping strategy for visible light  
photocatalysis

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Nanoscale Adv.*, 2025, 7, 4313

# Systematic investigation of ABO<sub>3</sub> perovskite synthesis to generalise a La and Rh co-doping strategy for visible light photocatalysis†

Thomas D. Small, <sup>a</sup> Mahmoud Adel Hamza, <sup>ab</sup> Yideng Shen, <sup>a</sup>  
Cameron J. Shearer <sup>\*a</sup> and Gregory F. Metha <sup>\*a</sup>

Photocatalysts present a promising method of producing cheap and green hydrogen. However, most highly-efficient photocatalysts are active to only UV light, which is only 4% of the power in sunlight. Consequently, commercial photocatalysis can only be achieved by developing efficient materials active to visible light (47% of sunlight). Co-doping La and Rh into the perovskite oxide, SrTiO<sub>3</sub> is known to create visible light photocatalysts as part of a Z-scheme system. Here, we rationally apply this strategy to SrTiO<sub>3</sub> and five other ABO<sub>3</sub> perovskites. The A and B-site elements (Sr, Ba, Zr, and Ti) were systematically varied within periodic groups to fabricate six different perovskites: SrZrO<sub>3</sub>, SrZr<sub>0.5</sub>Ti<sub>0.5</sub>O<sub>3</sub>, SrTiO<sub>3</sub>, BaZrO<sub>3</sub>, BaZr<sub>0.5</sub>Ti<sub>0.5</sub>O<sub>3</sub>, and BaTiO<sub>3</sub>. The elemental composition of the resulting perovskite affected particle size, crystallinity, morphology, and bandgap. All six perovskites were then co-doped with La and Rh and in every case the doped materials demonstrated red-shifted bandgap. Further, four La,Rh co-doped perovskites demonstrated photocatalytic hydrogen production under visible light (405 and 455 nm). Consequently, the La, Rh co-doping strategy was successfully generalised from SrTiO<sub>3</sub> to ABO<sub>3</sub> perovskites. La,Rh:BaTiO<sub>3</sub> exhibited the narrowest bandgap (2.58 eV) and the second highest photocatalytic activity. These properties establish La,Rh:BaTiO<sub>3</sub> as a potential commercial visible-light active photocatalyst.

Received 11th April 2025

Accepted 27th May 2025

DOI: 10.1039/d5na00338e

[rsc.li/nanoscale-advances](https://rsc.li/nanoscale-advances)

## 1 Introduction

Preventing global temperature from rising 1.5 °C by 2050 is critical to continued human survival.<sup>1</sup> This can only be delivered through an energy ecosystem of cost-competitive fossil fuel alternatives.<sup>1</sup> Green hydrogen is a renewable, energy-dense chemical fuel that is a key part of this future ecosystem.<sup>2,3</sup> However, green H<sub>2</sub> is still prohibitively expensive<sup>4</sup> rendering it currently unviable to either decarbonise the 2.5% of world CO<sub>2</sub> emissions already due to hydrogen production or establish green hydrogen as an integral part of a renewable energy economy.<sup>4</sup>

Photocatalysts are simple nanoparticulate semiconductors capable of producing green H<sub>2</sub> by absorbing sunlight to convert water into H<sub>2</sub> and O<sub>2</sub>.<sup>5</sup> Compared to more mature green hydrogen technologies, *e.g.* photovoltaic-powered electrolysis, photocatalysts provide an inexpensive means of hydrogen production.<sup>6</sup> However, state-of-the-art photocatalysts typically

report sunlight to hydrogen efficiency (STH) of 1–2%,<sup>7–9</sup> falling short of the 5–10% STH calculated by technoeconomic assessments for commercial implementation.<sup>6</sup> Recently InGaN nanowires have demonstrated an STH over 9%.<sup>10</sup> However, this was only achieved at concentrated solar conditions (33 suns and 70 °C). Further the nanowires were fabricated by molecular-beam epitaxy which could be expensive at scale. Regardless, the InGaN nanowires demonstrate that commercially viable STH values are achievable in photocatalysis.

High STH photocatalysts require narrow bandgap, high quantum efficiency, and redox stability.<sup>5</sup> Photocatalysts which demonstrate high Apparent Quantum Yield (AQY) and redox stability for overall water-splitting at standard conditions have been reported (0.56–96%).<sup>7,11,12</sup> However, such photocatalysts can only absorb UV light. UV-active photocatalysts are fundamentally unable to reach commercially viable STH as UV comprises only 4% of the power of sunlight.<sup>5</sup> Consequently, much of the recent work in commercial photocatalytic water-splitting focuses on developing visible light active photocatalysts.<sup>13–15</sup>

The AQY of visible light active photocatalysts are smaller and typically require non-standard photocatalytic conditions such as reduced pressure, the addition of sacrificial reagents, or the photocatalyst itself quickly degrades.<sup>9,16–18</sup> It is critical to develop visible light photocatalysts with the high AQY of UV

<sup>a</sup>Department of Chemistry, University of Adelaide, Adelaide, SA 5005, Australia.  
E-mail: [cameron.shearer@adelaide.edu.au](mailto:cameron.shearer@adelaide.edu.au); [greg.metha@adelaide.edu.au](mailto:greg.metha@adelaide.edu.au)

<sup>b</sup>Chemistry Department, Faculty of Science, Ain Shams University, Abbassia, Cairo, 11566, Egypt

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d5na00338e>

photocatalysts at standard conditions to establish commercial photocatalysis.<sup>14,19</sup>

Perovskite materials are relatively simple,  $ABX_3$ , rapidly maturing for use as highly efficient solar cells.<sup>20</sup> Accordingly,  $ABO_3$  perovskite oxides demonstrate some of the highest reported photocatalytic STH<sup>16</sup> and AQY.<sup>7,11</sup>  $ABO_3$  perovskites also exhibit design flexibility. The A and B-site elements can be varied to tune the material properties and optimise photocatalytic water-splitting activity.<sup>21</sup> Perovskites are also highly receptive to a wide variety of doping conditions.<sup>7,11,19,21–24</sup>

Co-doping La and Rh into  $SrTiO_3$  was recently demonstrated to confer visible light activity to the UV-only active base material without significantly compromising quantum efficiency.<sup>25</sup> This is because filled  $Rh^{3+}$  4d orbitals interact with O 2p orbitals, raising the valence band. Co-doped La cations, which can only occupy 3+ oxidation states, balance the Rh dopant charge. This suppresses the formation of  $Rh^{4+}$ , which would introduce a filled mid-gap state from the unpaired 4d electron into the electronic band structure.<sup>25</sup>  $La,Rh:SrTiO_3$  has demonstrated 30% AQY at 420 nm as part of a Z-scheme photocatalyst.<sup>25</sup> Applied to oxides, which are typically redox stable, La,Rh co-doping is a potentially powerful technique to fabricate photocatalysts which meet the two major concerns of visible light activity and high quantum efficiency. However, this method has so far been demonstrated for only a single, UV-active perovskite,  $SrTiO_3$ .

This study begins with synthesising, and then La,Rh co-doping, the well-studied  $SrTiO_3$ . The A and B-site elements were then systematically modified with same-group elements for the A and B-sites respectively. In total, six base perovskites were synthesised:  $SrZrO_3$ ,  $SrZr_{0.5}Ti_{0.5}O_3$ ,  $SrTiO_3$ ,  $BaZrO_3$ ,  $BaZr_{0.5}Ti_{0.5}O_3$ , and  $BaTiO_3$ . The six perovskites were then co-doped with La and Rh following the methods developed for  $SrTiO_3$ . This resulted in six doped perovskites:  $La,Rh:SrZrO_3$ ,  $La,Rh:SrZr_{0.5}Ti_{0.5}O_3$ ,  $La,Rh:SrTiO_3$ ,  $La,Rh:BaZrO_3$ ,  $La,Rh:BaZr_{0.5}Ti_{0.5}O_3$ , and  $La,Rh:BaTiO_3$ . The six pristine and six La,Rh co-doped materials were tested for sacrificial photocatalytic water-splitting under visible light (405 and 455 nm). Four of the La,Rh co-doped perovskites demonstrated  $H_2$  production under visible light. Overall, this work generalises La,Rh co-doping as a strategy for obtaining active visible light photocatalysts.

## 2 Experimental

### 2.1 Materials and reagents

All materials were used as purchased unless noted in the experimental.  $SrCO_3$  powder ( $\geq 99.9\%$ , Sigma-Aldrich).  $BaCO_3$  powder ( $\geq 99\%$ , Sigma-Aldrich).  $TiO_2$  powder ( $\geq 99.5\%$ , Aeroxide P25, Sigma-Aldrich).  $ZrO_2$  powder ( $\geq 99\%$ , Sigma-Aldrich).  $NaCl$  ( $\geq 99\%$ , Sigma-Aldrich).  $KCl$  ( $\geq 99\%$ , Chem-supply).  $Rh_2O_3 \cdot 5H_2O$  (99.99%, 59% Rh, Premion, Alfa Aesar).  $La_2O_3$  (99.99%, Sigma-Aldrich) and  $K_2PtCl_6$  ( $\geq 99.9\%$ , Sigma-Aldrich).

### 2.2 Perovskite synthesis

The overall synthesis scheme for  $La,Rh:ABO_3$  perovskites is shown in Fig. 1.

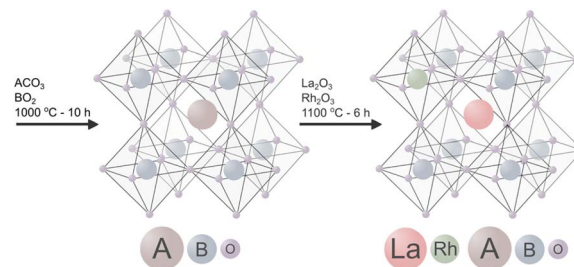


Fig. 1 Overall synthesis scheme for  $ABO_3$  perovskites and subsequent La,Rh co-doping.

Four  $ABO_3$  perovskites,  $SrZrO_3$ ,  $BaZrO_3$ ,  $SrTiO_3$ , and  $BaTiO_3$ , were synthesised in a solid-state reaction adapted from Wang *et al.*<sup>16</sup> The A-site reagent,  $SrCO_3$  or  $BaCO_3$  (preheated in air at 573 K for 1 h), and the B-site reagent,  $TiO_2$  or  $ZrO_2$ , were ground together with ethanol ( $3 \times 1$  mL) in a mortar and pestle for 20 min. The A/B element ratio was 1.05. The mixture was heated in an alumina crucible to 1423 K ( $5 \text{ K min}^{-1}$  to 523 K then  $10 \text{ K min}^{-1}$  to 1423 K) and held at that temperature for 10 h before cooling naturally to room temperature.

Two mixed B-site perovskites,  $SrZr_{0.5}Ti_{0.5}O_3$ , and  $BaZr_{0.5}Ti_{0.5}O_3$ , were synthesised in a molten salt flux adapted from O'Donnell *et al.*<sup>26</sup> The A-site reagent,  $SrCO_3$  or  $BaCO_3$ , in 10% mole excess, was mixed with equimolar  $TiO_2$  and  $ZrO_2$  and ground in a mortar and pestle with ethanol ( $2 \times 1$  mL) for 10 min. Subsequently an equimolar mixture of  $NaCl$  and  $KCl$  with a salt-to-product molar ratio of 20 : 1 was added to the reagents and the mixture was ground for a further 10 min. The mixture was heated in an alumina crucible to 1473 K ( $5 \text{ K min}^{-1}$  to 523 K then  $10 \text{ K min}^{-1}$  to 1473 K) and held at that temperature for 24 h before cooling naturally to room temperature. Excess salt was removed by washing the product with Milli-Q water and the product was collected by vacuum filtration. Repeated washings were performed until aq.  $AgNO_3$  (0.5 M) did not precipitate when added to the waste filtrate.

### 2.3 Co-doping synthesis

All six perovskites were co-doped with La and Rh in a solid-state synthesis adapted from Wang *et al.*<sup>16</sup> The perovskite was ground with  $La_2O_3$  (pre-treated by heating in air at 1432 K for 10 h) and  $Rh_2O_3 \cdot xH_2O$  (dehydrated in air at 973 K for 2 h) and ethanol ( $3 \times 1$  mL) in a mortar and pestle for 20 min. The mixture was then heated in an alumina crucible to 1473 K ( $5 \text{ K min}^{-1}$  to 523 K then  $10 \text{ K min}^{-1}$  to 1473 K) and held at that temperature for 6 h before cooling to room temperature ( $50 \text{ K min}^{-1}$ ). The target dopant levels were:  $La/(La + A) = 4 \text{ mol\%}$  and  $Rh/(Rh + B) = 4 \text{ mol\%}$ . The naming convention in this article follows:  $SrZrO_3$  is sometimes truncated to SZO.  $SrZr_{0.5}Ti_{0.5}O_3$  to SZT,  $SrTiO_3$  to STO,  $BaZrO_3$  to BZO.  $BaZr_{0.5}Ti_{0.5}O_3$  to BZT,  $BaTiO_3$  to BTO. Their co-doped counterparts follow suit (*e.g.*  $La,Rh:SZO$ ).

### 2.4 Characterisation

**2.4.1 Powder X-ray diffraction (PXRD).** XRD patterns were obtained with Co irradiation ( $\lambda$ : 1.78897 Å) from a D4 Endeavor



diffractometer (Bruker). Data was obtained from  $2\theta$  of 20 to  $110^\circ$ .

**2.4.2 Diffuse reflectance spectroscopy (DRS).** UV-Vis DRS spectra were used to determine the bandgap of each material before and after doping. Measurements were obtained using a spectrophotometer (Cary 5000 UV-Vis-NIR) with a Praying Mantis Diffuse Reflection Accessory (Harrick, DRP-SAP). A PTFE disc was used as the reflectance standard. For each measurement the sample holder was filled with *ca.* 15 mg of the powder sample and reflectance measurements were obtained from 200 to 800 nm. A Tauc transform was applied to the data and used to calculate the bandgap of each sample.<sup>27</sup>

**2.4.3 ICP-MS.** The elemental composition and quantification of the actual mol% of the perovskite elements (Sr, Ba, Zr, Ti) and dopants (La, Rh) were analysed by inductively coupled plasma mass spectrometry (ICP-MS, Agilent 8900x QQQ-ICP-MS). A measured mass (2–4 mg) of each sample was digested in 2 mL of aqua regia and sonicated for a few minutes at  $50\text{--}60^\circ\text{C}$ . This was diluted to 50 mL with 5%  $\text{HNO}_3$  and then further diluted in water to a final concentration of  $\sim 100\text{--}200$  ppb.

**2.4.4 Scanning electron microscopy (SEM).** The morphology, and particle size of the perovskites were measured using a High-Resolution Field Emission Scanning Electron Microscope equipped with EDX Silicon Drift Detectors (FEI-SEM Quanta 450). 100 particles for each photocatalyst were measured to investigate the particle size.

**2.4.5 Transmission electron microscopy.** High resolution images and elemental maps were obtained using an FEI Titan Themis STEM operating at 200 keV. The Titan is equipped with a Super-X EDS detector and a low background sample holder which minimize Cu background peaks and maximize X-ray collection efficiency. The perovskite powders were sonicated in Milli-Q water then dropped onto a 300-mesh copper grid with a lacey carbon support film. The water was evaporated in air before the sample was placed in the sample holder. EDS data were analysed using the Velox™ software from Thermo Fisher Scientific.

## 2.5 Photocatalytic hydrogen production

Photocatalytic hydrogen evolution was performed in a sealed batch reactor fitted with a quartz lid ( $1.7\text{ cm}^2$ ) for overhead-irradiation. In each reaction, 10 mg of sample was immersed in a 1 : 1 (by volume) mixture of distilled water and methanol and sonicated to homogeneous suspension. Air was evacuated from the reactor and replaced with Ar (1 atm). Each photocatalyst was surface-decorated with 1 wt% Pt nanoparticles by *in situ* photoreduction of aq.  $\text{K}_2\text{PtCl}_6$  ( $80.03\text{ }\mu\text{L}$ ,  $3.11\text{ mg mL}^{-1}$ ) for 1 h. Photoreduction was performed with a UV LED (365 nm,  $83\text{ mW cm}^{-2}$  HongKong UVET Co., UH-82F+L12). The stirring suspension was then irradiated with 405 and 455 nm LEDs. The evolved gases were sampled at 0 h, 1.5 h, and 3 h by gas chromatography (Agilent Technologies Micro GC 990, thermal conductivity detector, Ar carrier gas, molecular sieve 5 Å column).

The AQY measurements were performed in the same sealed batch reactor using a wider range of LED wavelengths. Before photocatalysis, air was evacuated from the reactor and replaced

with Ar (1 atm). The stirring suspension was then irradiated with one LED for up to 50 min. During the reaction, Ar flowed through the reaction cell at  $1\text{ mL min}^{-1}$ . The evolved gases were sampled every 2 min, starting at 0 min, and analysed by gas chromatography (Agilent Technologies Micro GC 990, thermal conductivity detector, Ar carrier gas, molecular sieve 5 Å column). In this system with constant flow of carrier gas, the evolved hydrogen is mixed with the carrier gas and its relative % is determined from calibrated data. This value is converted to a hydrogen production rate.

LEDs used: 365 nm ( $31.46\text{ mW cm}^{-2}$  HongKong UVET Co., UH-82F+L12). 405 nm ( $\text{mW cm}^{-2}$  HongKong UVET Co., UH-82F+L12). 430 nm ( $28.9\text{ mW cm}^{-2}$  Thorlabs, Inc). 455 nm ( $27.3\text{ mW cm}^{-2}$  Thorlabs, Inc). 470 nm ( $20.8\text{ mW cm}^{-2}$  Thorlabs, Inc). 505 nm ( $25.6\text{ mW cm}^{-2}$  Thorlabs, Inc). The powers were selected to keep a constant photon flux of  $6.25 \times 10^{19}\text{ }\gamma\text{ s}^{-1}\text{ cm}^{-2}$  across all LEDs used.

## 3 Results and discussion

### 3.1 Characterisation

**3.1.1 Goldschmidt tolerance factor.** The Goldschmidt tolerance factor ( $t$ ) indicates crystal stability, distortion, and morphology of a perovskite.<sup>28,29</sup> A  $t$  of 1 indicates ideal perovskite cubic crystallinity. A  $t > 1$  indicates hexagonal distortion while a  $t < 1$  indicates orthorhombic distortion.<sup>29</sup> The  $t$  for the six base  $\text{ABO}_3$  perovskites was calculated from the ionic radii of the A-site element ( $r_A$ ), The B-site element ( $r_B$ ) and the oxygen anions ( $r_O$ ):

$$t = \frac{(r_A + r_O)}{\sqrt{2}(r_B + r_O)} \quad (1)$$

The effect of co-doped materials on  $t$  is not reported in previous results focused on doping  $\text{SrTiO}_3$ .<sup>22,25,30</sup> Consequently, a modified equation ( $t'$ ) for the  $\text{La,Rh:ABO}_3$  perovskites were calculated by incorporating the La ionic radii ( $r_{\text{La}}$ ) and Rh ionic radii ( $r_{\text{Rh}}$ ) into the tolerance equation. The radii of each cation (dopant or base) in  $t'$  were weighted by stoichiometry. Following previous reports, it was assumed La occupies the A-site and Rh occupies the B-site.<sup>22,31</sup> The modified tolerance equation is:

$$t' = \frac{r_A \times n_A + r_{\text{La}} \times n_{\text{La}} + r_O}{\sqrt{2}(r_B \times n_{\text{Rh}} + r_{\text{Rh}} \times n_{\text{La}} + r_O)} \quad (2)$$

A-site elements have a coordination number (CN) of 12 and the B-site elements have a CN of 6 in a perovskite. A CN of 6 was used for the oxygen anions.<sup>28,29</sup> The resulting ionic radii are  $\text{Sr}^{2+}$ :  $1.44\text{ }\text{\AA}$ ,  $\text{Ba}^{2+}$ :  $1.61\text{ }\text{\AA}$ ,  $\text{Ti}^{4+}$ :  $0.605\text{ }\text{\AA}$ ,  $\text{Zr}^{4+}$ :  $0.72\text{ }\text{\AA}$ ,  $\text{La}^{3+}$ :  $1.36\text{ }\text{\AA}$  and  $\text{Rh}^{3+}$ :  $0.665\text{ }\text{\AA}$ .<sup>32</sup> The tolerance factors for the base perovskites are summarised in Table 1.

The calculated  $t$  for all 12 materials are close to 1, ranging from 0.95 to 1.06. This indicates all the photocatalysts have, or are close to, ideal cubic perovskite bulk crystallinity. STO and BZO have ideal values of 1. SZT and SZO have  $t < 1$  and likely incur slight orthorhombic distortion. Whereas BZT and BTO with  $t > 1$  have slight hexagonal distortion.



**Table 1** Goldschmidt tolerance factors of pristine perovskites ( $t$ ) and their La,Rh co-doped counterparts ( $t'$ )

| Photocatalyst | $t$ (a.u.) | $t'$ (a.u.) |
|---------------|------------|-------------|
| SZO           | 0.95       | 0.95        |
| BZO           | 1.00       | 1.00        |
| SZT           | 0.97       | 1.00        |
| BZT           | 1.03       | 1.06        |
| STO           | 1.00       | 1.00        |
| BTO           | 1.06       | 1.06        |

Co-doping La and Rh at 4 mol% does not significantly alter  $t$ . This results from two factors. (1) The similarity in ionic radii of the dopants to their respective A or B-site elements. (2) The small amount of dopants used (4 mol%). These calculations suggest that co-doping will not significantly alter the crystal structure of the base materials.

**3.1.2 Powder X-ray diffraction.** PXRD diffractions patterns for all 12 materials were obtained (Fig. 2). The titanates and zirconates were indexed to a cubic perovskite crystal structure (Fig. S1†), corroborating the cubic perovskite structure with slight distortions predicted by the Goldschmidt tolerance factor. The co-doped materials gave near-identical traces to their undoped counterparts, indicating that La,Rh co-doping does not compromise or alter the bulk crystallinity of the material. Doublet peaks were observed for SZT and La,Rh:SZT around 35, 52 and 67.5°. This may indicate SZT formed multiple perovskite phases related to separate zirconate and titanate phases. The doublet peaks were observed for doped and undoped samples so likely occurred during the base material synthesis. Additional peaks were also observed to a lesser extent for BZT, La,Rh:BZT, BTO, and La,Rh:BTO. The PXRD traces for SZO,<sup>33</sup> STO,<sup>34</sup> BZO,<sup>26</sup> BZT<sup>26</sup> and BTO<sup>35</sup> conform to traces previously reported.

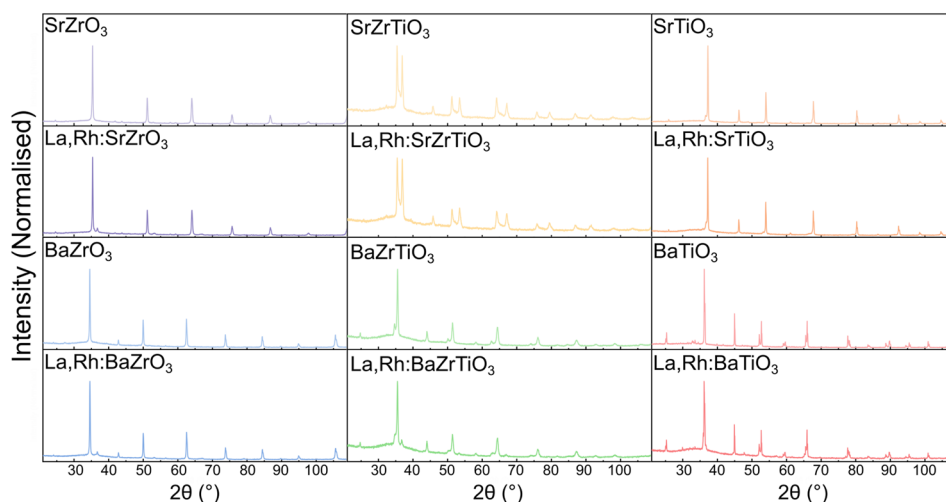
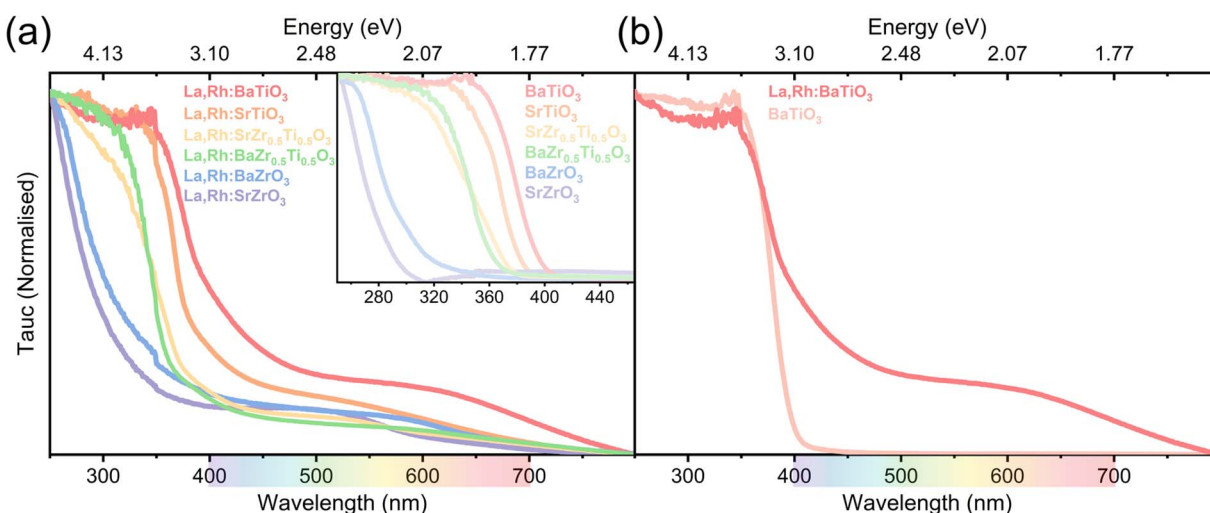
**Fig. 2** X-ray diffraction patterns of base  $\text{ABO}_3$  and La,Rh: $\text{ABO}_3$  perovskites.**Fig. 3** (a) Normalised Tauc plot of La,Rh: $\text{ABO}_3$  perovskites. The inset contains Tauc plots for the base perovskites. (b) The Tauc of La,Rh co-doped and undoped BTO are plotted to demonstrate the visible light absorption conferred by La,Rh co-doping.

Table 2 Characterised properties and photocatalytic performance of undoped perovskites

| Photocatalyst | <i>t</i> (a.u.) | Crystal structure | Bandgap (eV nm <sup>-1</sup> ) | Mode particle size (nm) | Particle morphology | 405 nm H <sub>2</sub> prod. (nmol h <sup>-1</sup> ) | 455 nm H <sub>2</sub> prod. (nmol h <sup>-1</sup> ) |
|---------------|-----------------|-------------------|--------------------------------|-------------------------|---------------------|-----------------------------------------------------|-----------------------------------------------------|
| SZO           | 0.95            | Orthorhombic      | 4.23/293                       | 291                     | Irregular           | 0.00                                                | 0.00                                                |
| BZO           | 1.00            | Cubic             | 4.07/305                       | 339                     | Irregular           | 0.00                                                | 0.00                                                |
| SZT           | 0.97            | Orthorhombic      | 3.32/374                       | 335                     | Cubic               | 0.00                                                | 0.00                                                |
| BZT           | 1.03            | Hexagonal         | 3.40/365                       | 382                     | Cubic               | 0.00                                                | 0.00                                                |
| STO           | 1.00            | Cubic             | 3.22/385                       | 253                     | Cubic               | 95.0                                                | 0.00                                                |
| BTO           | 1.06            | Hexagonal         | 3.09/401                       | 360                     | Cubic               | 79.3                                                | 0.00                                                |

**3.1.3 Diffuse reflectance spectroscopy.** UV-vis reflectance measurements were obtained for the perovskites (Fig. 3). Kubelka–Munk followed by Tauc transformations were applied and used to calculate the bandgap of the pristine (Table 2) and La,Rh co-doped photocatalysts (Table 3).<sup>27</sup> The measured bandgaps are consistent with previous reports in the literature for the base perovskites and La,Rh:STiO<sub>3</sub>.<sup>25,35–37</sup> The DRS data shows three broad trends (Fig. 3). (1) Going down the Group for the A-site element (*i.e.* Sr to Ba) narrows the bandgap. (2) Going down the Group for the B-site element (*i.e.* Ti to Zr) increases the bandgap, this effect is larger than the A-site substitution. (3) La,Rh co-doping for all six perovskites increases absorbance in the visible spectrum and narrows the bandgap.

These findings are exemplified by La,Rh:BTO and SZO. La,Rh:BTO comprises the heaviest A-site element and lightest B-site element and demonstrates the narrowest bandgap of 2.58 eV. SZO is undoped and comprises the lightest A-site element and heaviest B-site element; this results in the widest bandgap of 4.23 eV.

The Rh,La co-doping strategy successfully red-shifted the absorption of all 6 photocatalysts (Fig. 3a). This absorption was extended into visible light for La,Rh:SZT, La,Rh:BZT, La,Rh:STO and La,Rh:BTO. The perovskites from widest to narrowest bandgap are La,Rh:SZO, La,Rh:BZO, La,Rh:SZT, La,Rh:BZT, La,Rh:STO, La,Rh:BTO. The undoped perovskites follow an identical trend. La,Rh:STO and La,Rh:BTO demonstrated the greatest amount of visible light absorption and consequently have the greatest potential for visible light photocatalysis.

**3.1.4 Inductively coupled mass-spectrometry.** ICP-MS was used to determine the actual content of the perovskite elements and dopants (Fig. 4). The expected stoichiometries were A<sub>1</sub>B<sub>1</sub>O<sub>3</sub> for the base materials and A<sub>1</sub>Ti<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>3</sub> for the mixed oxides. The stoichiometry of Sr, Ba, Ti and Zr is very close to the

expected ratios – confirming the successful synthesis of the materials (Fig. 4).

The expected stoichiometries for the co-doped materials is La<sub>0.04</sub>Rh<sub>0.04</sub>A<sub>0.96</sub>B<sub>0.96</sub>O<sub>3</sub> (and La<sub>0.04</sub>Rh<sub>0.04</sub>A<sub>0.96</sub>Ti<sub>0.48</sub>Zr<sub>0.48</sub>O<sub>3</sub> for the mixed oxides). Doping had little appreciable effect on the base element stoichiometry (Table S1†). This corroborates the PXRD, suggesting that particle crystallinity, morphology, and lattice structure are not detrimentally affected by La,Rh co-doping.

ICP-MS data confirms the presence of La and Rh in all 6 co-doped samples, roughly in accordance with the expected stoichiometry (Fig. 4). This substantiates the cause of the red-shifted DRS spectra of the doped perovskites. The combined ICP and DRS data confirm Rh and La are correctly incorporated

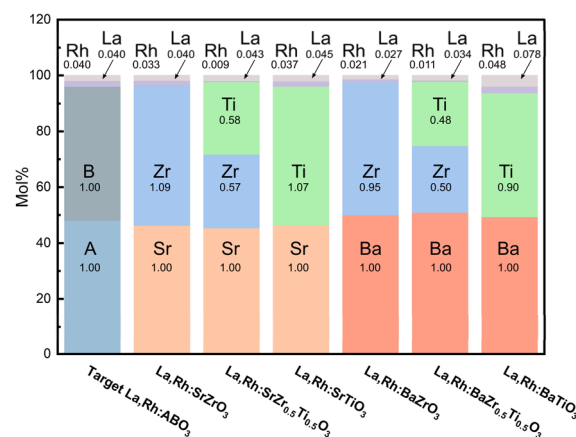


Fig. 4 ICP-MS derived mol% of elements comprising the La,Rh:ABO<sub>3</sub> perovskites. The corresponding stoichiometry is labelled in black (normalised to the A element, Sr or Ba).

Table 3 Characterised properties and photocatalytic performance of La,Rh co-doped perovskites

| Photocatalyst | <i>t</i> (a.u.) | Crystal structure | Bandgap (eV nm <sup>-1</sup> ) | Mode particle size (nm) | Size change (%) | Particle morphology | 405 nm H <sub>2</sub> prod. (nmol h <sup>-1</sup> ) | 455 nm H <sub>2</sub> prod. (nmol h <sup>-1</sup> ) |
|---------------|-----------------|-------------------|--------------------------------|-------------------------|-----------------|---------------------|-----------------------------------------------------|-----------------------------------------------------|
| La,Rh:SZO     | 0.95            | Orthorhombic      | 3.40/365                       | 347                     | +17.6           | Irregular           | 0.00                                                | 0.00                                                |
| La,Rh:BZO     | 1.00            | Cubic             | 3.32/374                       | 420                     | +21.3           | Irregular           | 0.00                                                | 0.00                                                |
| La,Rh:SZT     | 1.00            | Orthorhombic      | 2.94/422                       | 377                     | +11.8           | Cubic               | 66.6                                                | 0.00                                                |
| La,Rh:BZT     | 1.06            | Hexagonal         | 2.95/420                       | 386                     | +1.04           | Cubic               | 16.5                                                | 0.00                                                |
| La,Rh:STO     | 1.00            | Cubic             | 2.67/460                       | 350                     | +32.2           | Cubic               | 289.3                                               | 109.3                                               |
| La,Rh:BTO     | 1.06            | Hexagonal         | 2.58/480                       | 451                     | +22.4           | Cubic               | 195.4                                               | 42.2                                                |



into the atomic lattice of the base material, providing improved visible light absorption.

Generally, both titanates demonstrated dopant content closest to the expected stoichiometry. They were followed by the zirconates which were followed by the mixed-oxides. No systematic variation of La or Rh content was observed when comparing the strontium perovskites to the barium perovskites.

The Rh content in SZO, SZT, BZT, and BZO was lower (0.009–0.0021) than the expected stoichiometry (0.04). On the other hand, the two titanite samples had Rh in near-expected stoichiometry. This may indicate Ti is a better host element for Rh than Zr. That said, the Rh content in SZT and BZT was noticeably lower than SZO and BZO. This suggests mixed B-sites may suppress dopant incorporation. The La content in the mixed-oxides did not see a similar drop.

In all six samples the La content was higher than the corresponding Rh content. In general, the La content was closer to the expected stoichiometry than Rh. This could indicate La incorporation is more favourable than Rh incorporation. This could stem from the smaller ionic radius of  $\text{La}^{3+}$  than either of the A-site elements whereas  $\text{Rh}^{4+}$  is smaller than  $\text{Zr}^{4+}$  but larger than  $\text{Ti}^{3+}$ . However, it should then follow that the Rh content of the zirconates would be higher than the Rh content of the titanates. In fact, the opposite is true. Alternatively, Rh may be less digestible in aqua regia which could result in lower % observed. Three samples, SZT, STO, and BTO, demonstrated slightly excessive La stoichiometries of 0.043, 0.045, and 0.078. This may mean the generally higher La concentrations stem from ICP-MS matrix effects.

**3.1.5 SEM.** SEM images were obtained for all 12 samples. Representative SEM images of the 6 co-doped perovskites are provided in Fig. 5 (Fig. S2–S4† contain the SEM images for the undoped perovskites). The titanates and mixed-titanates particles appeared roughly cubic, with irregular morphology. In contrast, both zirconates showed much greater morphological irregularity, with many inter-grown particles (Fig. 5).

The SEM images were used to calculate the size distribution of each sample. The size distribution was fit to a log-normal distribution and the mode particle size of the fit was used to compare between samples. Both zirconates have the narrowest size distributions (Fig. S2†). BZT and BTO samples have a broader range of particle sizes than their Sr counterparts.

After La,Rh co-doping, all of the samples demonstrated a greater mode particle size, growing by 50–100 nm (Fig. 6). La,Rh:BZT was an exception, increasing in mode particle size by only 10 nm. This indicates that co-doping La,Rh could lead to increased particle sizes. However, La and Rh were doped at temperatures 50 K higher than the synthesis temperature of the base perovskites and for 6 more hours. Additional time spent at elevated temperature could also increase particle size.

Photocatalysts with Ba at the A-site were larger than their Sr counterparts in all cases (Fig. 6). The larger atomic radius of Ba (268 pm) compared to Sr (249 pm) is a potential cause. The synthetic conditions were adapted from conditions optimised for  $\text{SrTiO}_3$ .  $\text{BaTiO}_3$  and  $\text{BaCO}_3$  also have lower melting points than  $\text{SrTiO}_3$  and  $\text{SrCO}_3$ . This may indicate smaller  $\text{BaTiO}_3$  could be obtained from lower synthesis temperatures. Zr and Ti have near identical atomic radii (186 and 187 pm respectively).

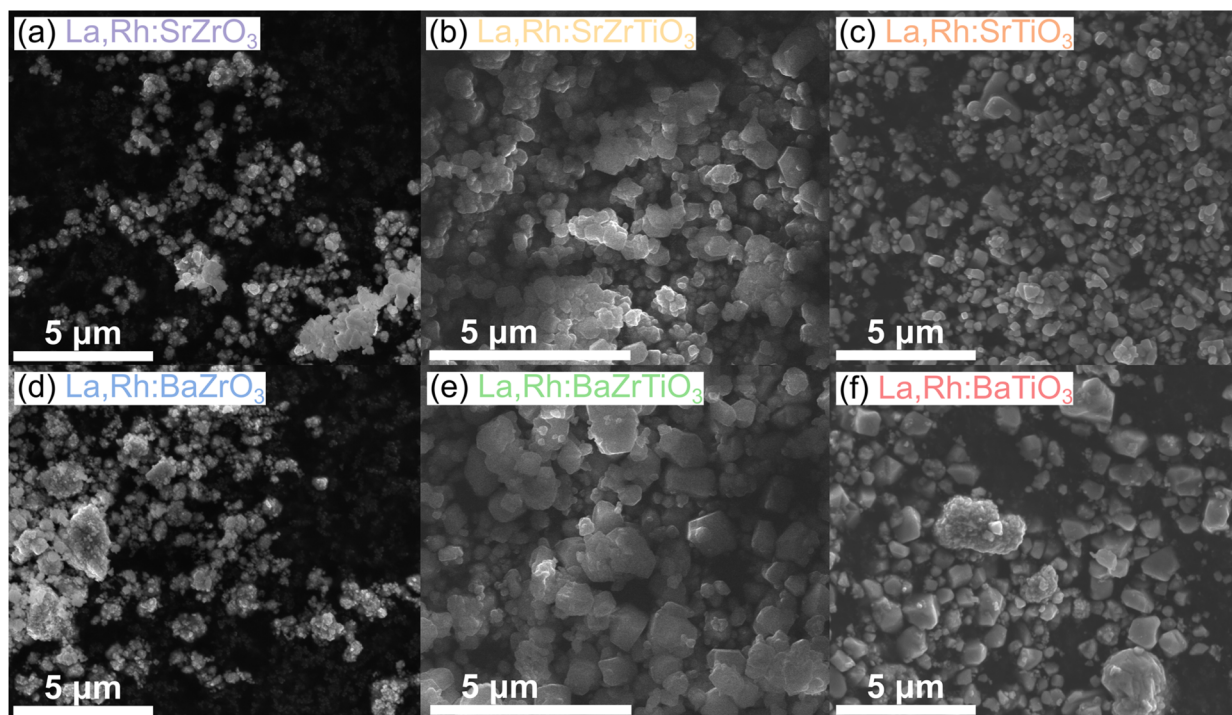



Fig. 5 SEM images of La,Rh co-doped perovskites. (a) La,Rh:SrZrO<sub>3</sub>. (b) La,Rh:SrZrTiO<sub>3</sub>. (c) La,Rh:SrTiO<sub>3</sub>. (d) La,Rh:BaZrO<sub>3</sub>. (e) La,Rh:BaZrTiO<sub>3</sub>. (f) La,Rh:BaTiO<sub>3</sub>.



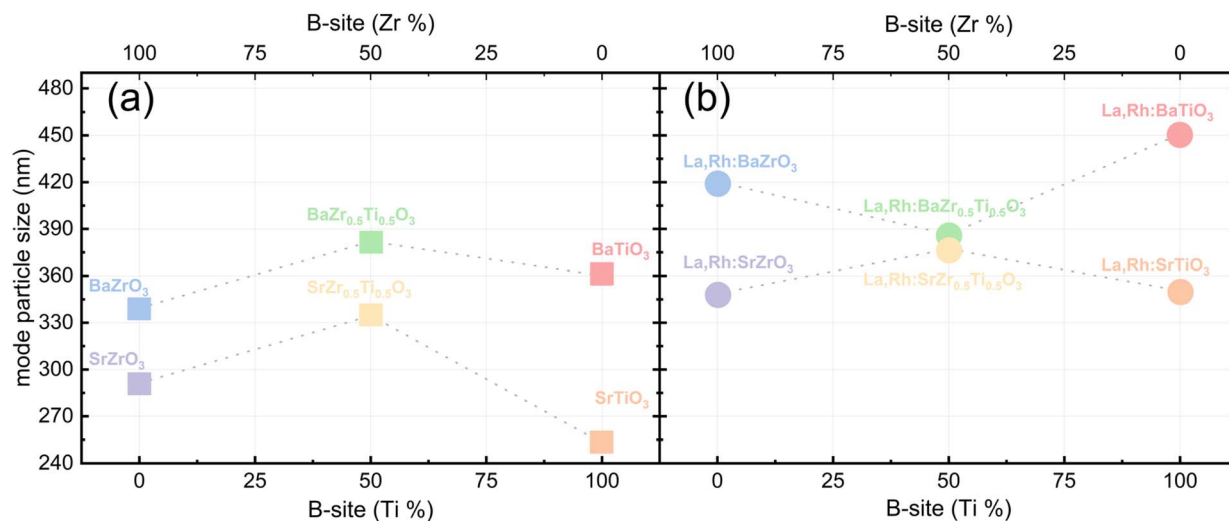


Fig. 6 Mode perovskite particle size comparison. (a) Undoped perovskites (b) La,Rh co-doped perovskites.

Consequently, the AZrO<sub>3</sub> perovskites tended to similar sizes of their ATiO<sub>3</sub> counterparts.

For the pristine perovskites, both mixed B-site perovskites exhibited a particle size increase. Given the atomic radius similarity of Ti and Zr, the size increase is attributed to the longer synthesis time (24 h vs. 10 h) needed to fabricate the mixed-oxide perovskites.

The co-doped photocatalysts reverse this trend. The mixed B-site perovskites are smaller compared to their AZO and ATO counterparts. That said, the AZT perovskites also demonstrate the smallest post-doping particle size increase (Table 3, *vide*

*infra*). The smaller La,Rh:AZT size change is also attributed to the longer base material syntheses time.

**3.1.6 TEM.** TEM images were obtained for the best performing sample for photocatalysis at 405 nm – La,Rh:SrTiO<sub>3</sub> (Fig. 7a). The ultrahigh-resolution images reveal the elemental distribution and atomic lattice of the La,Rh co-doped particles. An EDS map of a La,Rh:SrTiO<sub>3</sub> particle reveals low dopant incorporation in the particle core with a Rh-rich shell, penetrating from approx. 5–20 nm into the particle which indicates the formation of a dopant-rich shell surrounding a near-pristine SrTiO<sub>3</sub> core (Fig. 7b). A 110 nm line profile of the EDS net intensity across the same particle (white arrow, Fig. 7b) reveals

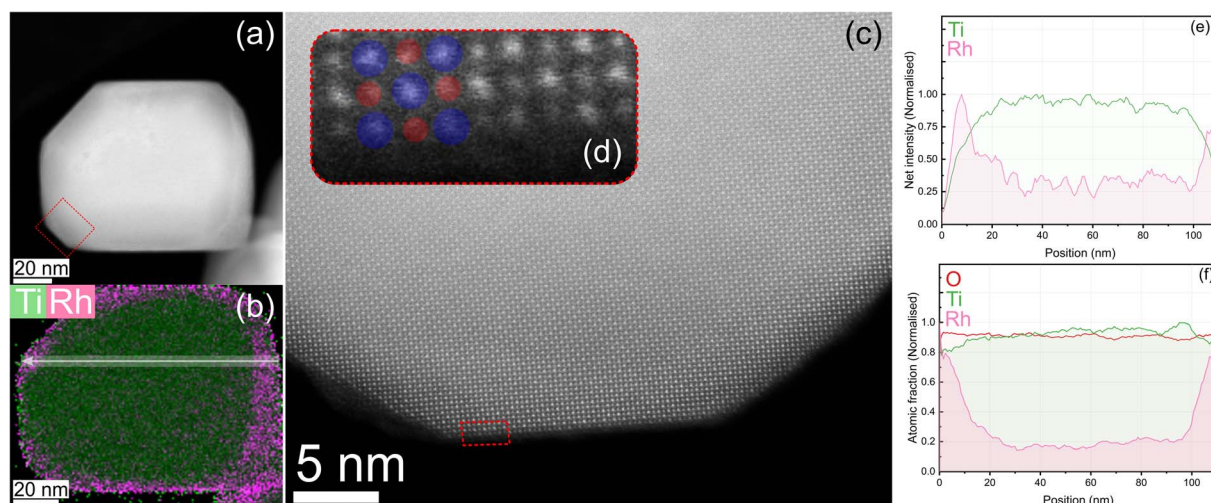


Fig. 7 (a) High-angle annular dark-field (HAADF) TEM image of a representative La,Rh:SrTiO<sub>3</sub> particle. (b) EDS map of the particle. (c) La,Rh:SrTiO<sub>3</sub> atomic lattice of the region outlined in the red box in (a). (d) Atomic-resolution image of the red dotted-box in (c), depicting the cubic structure of the La,Rh-concentrated exterior of the particle. The A-site elements (Sr and La) are identified with blue circles and the B-site elements (Ti and Rh) are identified with red circles. The A-site elements both have higher atomic numbers than the corresponding B-site elements and therefore appear brighter in a HAADF image. (e) EDS line profile of net signal intensity for Ti and Rh across the arrow in (b). The white shaded region around the arrow depicts the integration area. A moving average (data window = 5) was applied to smooth the data. (f) Normalised atomic fraction EDS line profile. A moving average (data window = 5) was applied to smooth the data.



higher Rh content at the particle edges (0–20 nm and 100–110 nm) than the core (Fig. 7e). This was also observed to a lesser extent for La (Fig. S5a and b†). In contrast, the signal for Ti is lower at the edges and reaches a maximum towards the particle core (20–95 nm). The signal shape observed for Ti was also observed for Sr and O (Fig. S5a†). In a particle with a homogeneous elemental distribution a lower net intensity for STEM-EDS is expected at the edges as there will be less material to interact with the electron beam than the core. Therefore, the higher signal for Rh at the particle edge reflects an inhomogeneous (surface concentrated) elemental distribution. The elemental distribution across the line profile was also measured in atomic fraction which weights the signal ( $\text{mol}_{\text{element}}/\text{mol}_{\text{total}}$ ) and therefore avoids changes to signal intensity as a function of the amount of particle which interacts with the electron beam. The atomic fraction line profiles corroborate the core-shell morphology observed in the net intensity line profile (Fig. 7f). Further, at the edges the Ti signal is slightly lower than the O signal (which is essentially flat across the entire profile), which indicates a slight reduction in edge Ti species correlated to Rh-doping. The atomic fraction line profile also indicates minimal La/Rh content (approximately  $\leq 0.5 \text{ mol}\%$ ) outside of the edges of the line profile (Fig. S5b†). Note that surface Rh/La on the top particle edge (*i.e.* edge facing the reader) will also produce an EDS signal and therefore surface La/Rh atoms will also contribute to the signal in the core region of the line profile. Consequently, these results indicate that trace amounts, if any, of La and Rh are incorporated into the particle core. The core-shell finding is consistent with previous reports on La,Rh:SrTiO<sub>3</sub> and the synthetic mechanism of doping and may be responsible for lower absorption of visible light compared to UV absorption observed for all six La,Rh co-doped materials (Fig. 3a).<sup>22</sup>

Maintaining the perovskite crystallinity of the host material in the dopant-rich surface is critical to suppressing chemical or crystalline defects.<sup>25,38</sup> Further, perovskite morphology enables facet-specific electronics which improve charge-transfer

efficiency.<sup>7,34</sup> The atomic lattice for STO and La,Rh:STO maintained cubic perovskite crystallinity. The shell lattice shows no discernible difference from the core lattice (Fig. 7c). Further, the typical cubic crystal structure of SrTiO<sub>3</sub> is identifiable in the dopant-rich shell (Fig. 7d). This demonstrates that La and Rh are incorporated into the ATiO<sub>3</sub> perovskite without appreciable disruption to the crystal lattice.

Two-step solid-state doping methods typically produce core-shell particles comprising a pristine core and the dopant-rich shell.<sup>19,22,24,39</sup> Doping occurs in the second step by diffusion of the dopants into the base material's structure. The photocatalytic efficacy of core-shell nanoparticles is debated. Computational modelling has found such structures to be either advantageous or deleterious.<sup>19,40</sup> More research is needed to determine the photocatalytic efficacy of particles with core-shell morphology.

### 3.2 Photocatalysis

Photocatalytic hydrogen evolution for all 12 samples was performed using 405 and 455 nm LEDs under sacrificial conditions (1 : 1 CH<sub>3</sub>OH : H<sub>2</sub>O, Fig. 8). Pt nanoparticles were photo-deposited *in situ* during photocatalysis at 1 wt%. Pt nanoparticles have proven efficacy in enabling catalytic hydrogen production.<sup>41</sup> Visible wavelengths were selected to confirm co-doping La and Rh conferred visible light activity.

As expected, all six undoped perovskites were photocatalytically inactive at 455 nm (Fig. 8b). Whereas four La,Rh co-doped materials (La,Rh:SrZr<sub>0.5</sub>Ti<sub>0.5</sub>O<sub>3</sub>, La,Rh:BaZr<sub>0.5</sub>Ti<sub>0.5</sub>O<sub>3</sub>, La,Rh:SrTiO<sub>3</sub> and La,Rh:BaTiO<sub>3</sub>) achieved visible light hydrogen production at 405 nm. The co-doped titanates, La,Rh:SrTiO<sub>3</sub> and La,Rh:BaTiO<sub>3</sub> also demonstrated H<sub>2</sub> evolution at 455 nm. On the other hand, La,Rh:SrZrO<sub>3</sub> and La,Rh:BaZrO<sub>3</sub> did not produce H<sub>2</sub> at any wavelength. These results are all consistent with the DRS-determined bandgaps for each photocatalyst (Table 3, *vide infra*).

Photocatalysis was performed for up to 3 h with close to linear production which indicates the potential long-term

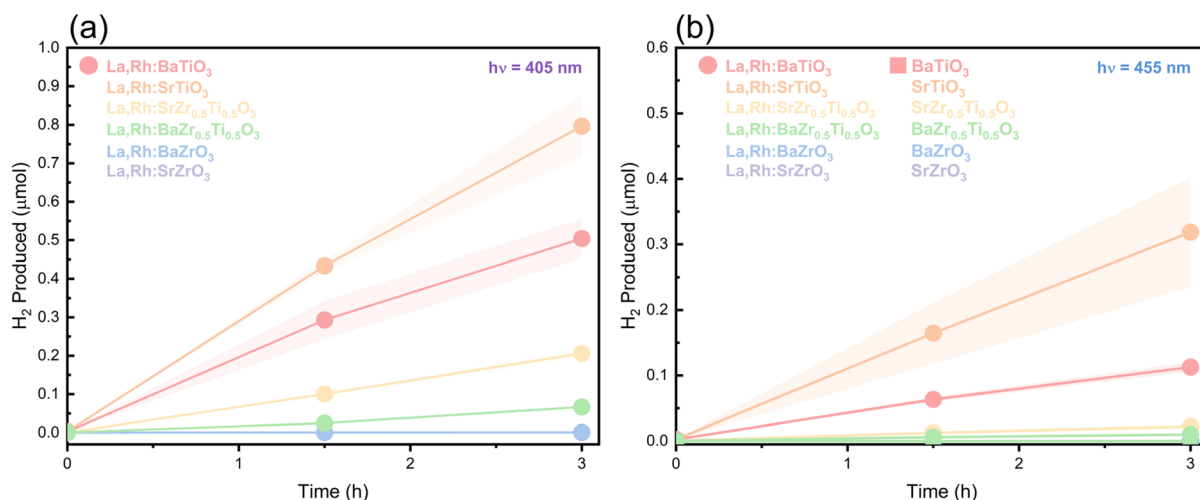


Fig. 8 Photocatalytic H<sub>2</sub> evolution of various perovskites from a 1 : 1 H<sub>2</sub>O and CH<sub>3</sub>OH mix using 405 (a) and 455 nm light (b). The shaded areas depict standard error. Conditions: 7 mg photocatalyst, 405 (228.0 mW cm<sup>-2</sup>) or 455 (88.4 mW cm<sup>-2</sup>) nm LED.



activity of the materials.  $\text{ABO}_3$  and  $\text{La,Rh:SrTiO}_3$  perovskites have demonstrated long-term activity in the literature (up to 1000 + h), which provides further support to the long-term viability of the materials.<sup>8,42</sup> However further testing of the photocatalysts described here is necessary to confirm similar longevity.

Two undoped materials,  $\text{SrTiO}_3$  and  $\text{BaTiO}_3$ , unexpectedly evolved small amounts hydrogen at 405 nm (Table 2). The titanates have the narrowest bandgaps of the undoped photocatalysts and the LEDs emit in a Gaussian distribution, peak: 405 nm FWHM: 10.8 nm (Fig. S6†). Consequently, some UV photons present in the 405 nm LED could be absorbed and therefore explain the activity at 405 nm.

The most active samples were  $\text{La,Rh:SrTiO}_3$  and  $\text{La,Rh:BaTiO}_3$ . These materials have the narrowest bandgaps and Ti as the B-site element. Further, both materials outperform their pristine counterparts at 405 and 455 nm.  $\text{La,Rh:BaTiO}_3$ , which demonstrated the greatest visible light absorption, and the 2<sup>nd</sup> highest photocatalytic activity was then compared against  $\text{La,Rh:SrTiO}_3$  over a range of LED wavelengths from 365–505 nm (Fig. 9). AQY was obtained at each wavelength and plotted with the DRS data, as shown in Fig. 9.

Both  $\text{La,Rh}$  co-doped materials demonstrated visible light activity, evolving  $\text{H}_2$  up to 505 nm which is well into the visible region of sunlight.  $\text{La,Rh:BaTiO}_3$  shows lower activity at shorter wavelengths, but as the wavelength of light extends into the visible region it begins to outperform  $\text{La,Rh:SrTiO}_3$ . This is in line with the absorption profiles obtained in Fig. 3. However, the AQY also drops as the light absorption falls which is also in line with UV-Vis absorption data. This indicates synthetic modifications which increase the visible light absorption, bringing it in line with the UV light absorption, could yield better catalysts. Fig. S7† contains the gas chromatographs of the  $\text{H}_2$  peaks for photocatalysis of  $\text{La,Rh:SrTiO}_3$  at 455, 470 and 505 nm and confirms that the  $\text{H}_2$  peak is readily distinguishable from the baseline trace and dark peak at lower AQY. The bandgaps of  $\text{La,Rh:SrTiO}_3$  and  $\text{La,Rh:BaTiO}_3$  were determined

to be 2.67 eV (460 nm) and 2.58 eV (480 nm) respectively. This could indicate absorbance and activity at 505 nm is due to  $\text{Rh}^{4+}$  defect states rather than  $\text{Rh}^{3+}$  valence band states and the former are correlated to lower activity.<sup>43</sup> However, the relatively broad spectral output of the 505 nm LED depicted in Fig. S6† means some photons will have sufficient energy to excite the  $\text{Rh}^{3+}$  modified bandgap, particularly for  $\text{La,Rh:BaTiO}_3$ , which could also explain the activities observed. The AQY obtained here for  $\text{La,Rh:SrTiO}_3$  is lower than the AQY reported for the same material by Wang *et al.* (30%).<sup>16</sup> However, the latter material was used as a component in a Z-scheme system which used conductive gold mediator and was measured at reduced pressure.

Given the better light absorption profile and similar photocatalytic rates of  $\text{La,Rh:BaTiO}_3$  compared with  $\text{La,Rh:SrTiO}_3$ ,  $\text{La,Rh:BaTiO}_3$  is a promising alternative candidate for hydrogen evolution in a Z-scheme photocatalyst.  $\text{La,Rh:BaTiO}_3$  was fabricated using synthetic conditions optimised for  $\text{La,Rh:SrTiO}_3$ . Tailoring the synthetic conditions to  $\text{La,Rh:BaTiO}_3$  could further improve the efficiency of  $\text{La,Rh:BaTiO}_3$ .

## 4 Discussion

6 base perovskites were synthesised and the effect of systematically varying both the A and B sites was investigated. For the A-site element, moving down group 2 on the periodic table from Sr to Ba was found to narrow the bandgap. The opposite was true for the B-site element. Moving up the Group 4 elements to Zr from Ti was found to narrow the bandgap. Consequently,  $\text{BaTiO}_3$  had the narrowest bandgap of the six perovskites tested. Ti-containing perovskites were found to achieve greater photocatalytic hydrogen production. This activity tracks with bandgap, Goldschmidt tolerance factor (*t*), and particle size. Only STO and BTO have bandgaps able to absorb 405 nm light. STO are smaller particles and attains an ideal *t* of 1 (Table 2).

The 6 perovskites were then co-doped with La and Rh, characterised, and tested for photocatalytic hydrogen evolution (Table 3). Bandgap narrowing from  $\text{La,Rh}$  co-doping was previously only established for  $\text{SrTiO}_3$ . The combined DRS and ICP-MS, results of  $\text{La,Rh:STO}$  and 5 other  $\text{La,Rh:ABO}_3$  perovskites successfully generalise this bandgap narrowing strategy to  $\text{ABO}_3$  perovskites. PXRD, SEM and TEM measurements show  $\text{La,Rh}$  co-doping doesn't significantly alter bulk crystallinity, particle morphology or particle size. TEM elemental mapping for  $\text{La,Rh:SrTiO}_3$  revealed the doped particles comprise base material cores surrounded by dopant rich shells. Visible light (405 and 455 nm) photocatalytic hydrogen evolution was demonstrated for four perovskites,  $\text{La,Rh:SrZr}_{0.5}\text{Ti}_{0.5}\text{O}_3$ ,  $\text{La,Rh:BaZr}_{0.5}\text{Ti}_{0.5}\text{O}_3$ ,  $\text{La,Rh:SrTiO}_3$  and  $\text{La,Rh:BaTiO}_3$ .

The four active materials at 405 nm demonstrated  $\text{H}_2$  activity rates in order of  $\text{La,Rh:BZT} < \text{La,Rh:SZT} < \text{La,Rh:BTO} < \text{La,Rh:STO}$ . Particle morphology was similar across all four samples. Particle size, likewise, does not explain the relative activities; for example,  $\text{La,Rh:BTO}$  has the largest particles but reaches the second highest production rate. Ba appears to be a less efficient A-site element than Sr. Of the four active co-

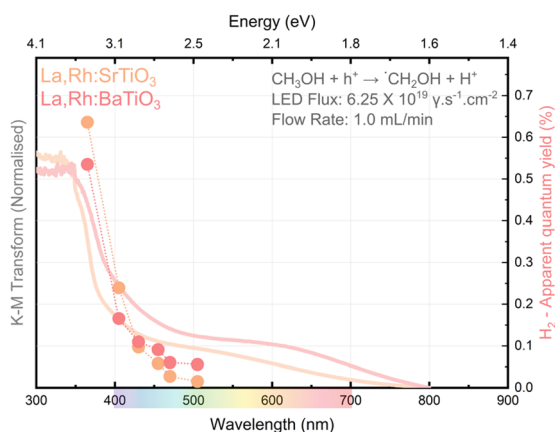


Fig. 9 Kubelka–Munk transform of UV-Vis diffuse reflectance and wavelength dependence on apparent quantum yield (AQY) of  $\text{La,Rh:SrTiO}_3$  and  $\text{La,Rh:BaTiO}_3$  from 365–505 nm. 7 mg photocatalyst, varying LED wavelength, constant photon flux ( $6.25 \times 10^{19} \gamma \text{ s}^{-1} \text{ cm}^{-2}$ ).



doped materials, perovskites with A-site Sr have close to ideal  $t$ . Their Ba equivalents demonstrated slight distortion. The  $H_2$  activities at 455 nm reflect the latter point. As the  $BaBO_3$  perovskites were uniformly larger than their  $SrBO_3$  counterparts, this may indicate photocatalytic improvements could be achieved with reduced particle size of  $BaBO_3$  perovskites.

Finally, the novel material  $La,Rh:BTO$  exhibits the most favourable bandgap for operation under solar radiation, as exemplified by its improved performance at 470 and 505 nm (Fig. 9). Further, Ti at the B-site was found to be more favourable for charge separation in comparison with a mixed B-site analogue. The synthetic conditions used were based on the synthesis and doping of  $SrTiO_3$ . Synthetic conditions tuned to  $BaTiO_3$  may improve quantum efficiency and enable the material to make full use of its bandgap.

## 5 Conclusion

Six base perovskites were synthesised:  $SrZrO_3$ ,  $SrZr_{0.5}Ti_{0.5}O_3$ ,  $SrTiO_3$ ,  $BaZrO_3$ ,  $BaZr_{0.5}Ti_{0.5}O_3$ , and  $BaTiO_3$ . A and B-site variation was found to modify particle size, morphology, crystallinity, and the bandgap. The perovskite bandgap was determined to be tuneable by up to 108 nm through A and B-site variation.

The six perovskites were then co-doped with La and Rh following the methods developed for  $SrTiO_3$ . This resulted in six doped perovskites:  $La,Rh:SrZrO_3$ ,  $La,Rh:SrZr_{0.5}Ti_{0.5}O_3$ ,  $La,Rh:SrTiO_3$ ,  $La,Rh:BaZrO_3$ ,  $La,Rh:BaZr_{0.5}Ti_{0.5}O_3$ , and  $La,Rh:BaTiO_3$ . The bandgap of all six perovskites was successfully narrowed – redshifting the bandgap by ca. 60–80 nm. Additionally, co-doping was found to increase particle size slightly and maintain base particle morphology and crystallinity.

Finally, all 12 materials were tested for sacrificial photocatalytic water-splitting under visible light (405 and 455 nm). Of the six doped materials, the two doped titanates,  $La,Rh:SrTiO_3$  and  $La,Rh:BaTiO_3$ , achieved the best performance. This trend was followed for the six base counterparts. Further, 4  $La,Rh$ -doped perovskites demonstrated  $H_2$  production under visible light. Overall, this work generalises  $La,Rh$  co-doping as a strategy for obtaining active visible light perovskite oxides.

The high performance of  $BaTiO_3$  and  $La,Rh:BaTiO_3$  is noteworthy, especially at longer wavelengths. The two photocatalysts are redshifted, close-analogues of the better studied  $SrTiO_3$  and  $La,Rh:SrTiO_3$ . Numerous modifications to  $SrTiO_3$ , such as synthesis under flux-conditions and co-catalyst optimisation over the past 20 years have culminated in a material which achieves a 96% AQY for UV-light. Given the similarity of  $BaTiO_3$  to  $SrTiO_3$  similar AQY improvements are possible and in conjunction with the narrower bandgap of  $BaTiO_3$  and  $La,Rh:BaTiO_3$  could lead to a material with a higher theoretical STH. Detailed investigations of  $La,Rh:BaTiO_3$  such as optimised syntheses could lead to new perovskites which outperform  $SrTiO_3$  for visible light water-splitting.

## Data availability

All data is provided in the ESI .xlsx file.†

## Conflicts of interest

The authors have no conflicts to declare.

## Acknowledgements

This work was supported by funding from the Future Fuels CRC. TDS acknowledges the Future Fuels CRC for awarding a post-graduate scholarship. The authors acknowledge the facilities of Adelaide Microscopy (University of Adelaide). CJS acknowledges funding support from The Australian Research Council (ARC) for a Future Fellowship (FT190100854).

## References

- 1 IEA, *Net Zero by 2050*, IEA, 2021, <https://www.iea.org/reports/net-zero-by-2050>.
- 2 BP, *BP - Energy Outlook 2020*, 2020, <https://www.bp.com/content/dam/bp/business-sites/en/global/corporate/pdfs/energy-economics/energy-outlook/bp-energy-outlook-2020.pdf>.
- 3 DCCEW 2024, *National Hydrogen Strategy 2024*, Department of Climate Change, Energy, the Environment and Water, Canberra, CC BY 4.0., [www.dccew.gov.au/sites/default/files/documents/national-hydrogen-strategy-2024.pdf](http://www.dccew.gov.au/sites/default/files/documents/national-hydrogen-strategy-2024.pdf).
- 4 IEA, *Global Energy Review 2025*, <https://www.iea.org/reports/global-energy-review-2025>.
- 5 Q. Wang and K. Domen, Particulate Photocatalysts for Light-Driven Water Splitting: Mechanisms, Challenges, and Design Strategies, *Chem. Rev.*, 2020, **120**, 919–985, DOI: [10.1021/acs.chemrev.9b00201](https://doi.org/10.1021/acs.chemrev.9b00201).
- 6 B. A. Pinaud, *et al.*, Technical and economic feasibility of centralized facilities for solar hydrogen production via photocatalysis and photoelectrochemistry, *Energy Environ. Sci.*, 2013, **6**, 1983–2002, DOI: [10.1039/c3ee40831k](https://doi.org/10.1039/c3ee40831k).
- 7 T. Takata, *et al.*, Photocatalytic water splitting with a quantum efficiency of almost unity, *Nature*, 2020, **581**, 411–414, DOI: [10.1038/s41586-020-2278-9](https://doi.org/10.1038/s41586-020-2278-9).
- 8 Q. Wang, *et al.*, Particulate Photocatalyst Sheets Based on Carbon Conductor Layer for Efficient Z-Scheme Pure-Water Splitting at Ambient Pressure, *J. Am. Chem. Soc.*, 2017, **139**, 1675–1683, DOI: [10.1021/jacs.6b12164](https://doi.org/10.1021/jacs.6b12164).
- 9 J. Liu, *et al.*, Metal-free efficient photocatalyst for stable visible water splitting via a two-electron pathway, *Science*, 2015, **347**, 970–974, DOI: [10.1126/science.aaa3145](https://doi.org/10.1126/science.aaa3145).
- 10 P. Zhou, *et al.*, Solar-to-hydrogen efficiency of more than 9% in photocatalytic water splitting, *Nature*, 2023, **613**, 66–70, DOI: [10.1038/s41586-022-05399-1](https://doi.org/10.1038/s41586-022-05399-1).
- 11 H. Kato, K. Asakura and A. Kudo, Highly Efficient Water Splitting into  $H_2$  and  $O_2$  over Lanthanum-Doped  $NaTaO_3$  Photocatalysts with High Crystallinity and Surface Nanostructure, *J. Am. Chem. Soc.*, 2003, **125**, 3082–3089, DOI: [10.1021/ja027751g](https://doi.org/10.1021/ja027751g).
- 12 Y. Sakata, *et al.*, Remarkable improvement of the photocatalytic activity of  $Ga_2O_3$  towards the overall splitting of  $H_2O$ , *ChemSusChem*, 2011, **4**, 181–184, DOI: [10.1002/cssc.201000258](https://doi.org/10.1002/cssc.201000258).



- 13 H. Shi, *et al.*, Visible Light Photoanode Material for Photoelectrochemical Water Splitting: A Review of Bismuth Vanadate, *Energy Fuels*, 2022, **36**, 11404–11427, DOI: [10.1021/acs.energyfuels.2c00994](https://doi.org/10.1021/acs.energyfuels.2c00994).
- 14 J. Xiao, T. Hisatomi and K. Domen, Narrow-Band-Gap Particulate Photocatalysts for One-Step-Excitation Overall Water Splitting, *Acc. Chem. Res.*, 2023, **56**, 878–888, DOI: [10.1021/acs.accounts.3c00011](https://doi.org/10.1021/acs.accounts.3c00011).
- 15 K. Rajeshwar, P. A. Maggard and S. O'Donnell, Search of the "Perfect" Inorganic Semiconductor/Liquid Interface for Solar Water Splitting, *Electrochem. Soc. Interface*, 2021, **30**, 47–51, DOI: [10.1149/2.f07211if](https://doi.org/10.1149/2.f07211if).
- 16 Q. Wang, *et al.*, Scalable water splitting on particulate photocatalyst sheets with a solar-to-hydrogen energy conversion efficiency exceeding 1%, *Nat. Mater.*, 2016, **15**, 611–615, DOI: [10.1038/nmat4589](https://doi.org/10.1038/nmat4589).
- 17 Q. Wang, *et al.*, Oxy sulfide photocatalyst for visible-light-driven overall water splitting, *Nat. Mater.*, 2019, **18**, 827–832, DOI: [10.1038/s41563-019-0399-z](https://doi.org/10.1038/s41563-019-0399-z).
- 18 K. Chen, *et al.*, Overall Water Splitting by a SrTaO(2)N-Based Photocatalyst Decorated with an Ir-Promoted Ru-Based Cocatalyst, *J. Am. Chem. Soc.*, 2023, **145**, 3839–3843, DOI: [10.1021/jacs.2c11025](https://doi.org/10.1021/jacs.2c11025).
- 19 S. O'Donnell, *et al.*, Prediction and Kinetic Stabilization of Sn(II)-Perovskite Oxide Nanoshells, *Chem. Mater.*, 2022, **34**, 8054–8064, DOI: [10.1021/acs.chemmater.2c02192](https://doi.org/10.1021/acs.chemmater.2c02192).
- 20 Y. Wang, *et al.*, Direct Solar Hydrogen Generation at 20% Efficiency Using Low-Cost Materials, *Adv. Energy Mater.*, 2021, **11**, 2101053, DOI: [10.1002/aenm.202101053](https://doi.org/10.1002/aenm.202101053).
- 21 Z. Wang, *et al.*, Advances in engineering perovskite oxides for photochemical and photoelectrochemical water splitting, *Applied Physics Reviews*, 2021, **8**, 021320, DOI: [10.1063/5.0039197](https://doi.org/10.1063/5.0039197).
- 22 Q. Wang, T. Hisatomi, S. S. K. Ma, Y. Li and K. Domen, Core/Shell Structured La- and Rh-Codoped SrTiO<sub>3</sub> as a Hydrogen Evolution Photocatalyst in Z-Scheme Overall Water Splitting under Visible Light Irradiation, *Chem. Mater.*, 2014, **26**, 4144–4150, DOI: [10.1021/cm5011983](https://doi.org/10.1021/cm5011983).
- 23 B. Modak and S. K. Ghosh, Enhancement of Visible Light Photocatalytic Activity of SrTiO<sub>3</sub>: A Hybrid Density Functional Study, *J. Phys. Chem. C*, 2015, **119**, 23503–23514, DOI: [10.1021/acs.jpcc.5b06667](https://doi.org/10.1021/acs.jpcc.5b06667).
- 24 A. S. Alotabi, *et al.*, Reduction and Diffusion of Cr-Oxide Layers into P25, BaLa(4)Ti(4)O(15), and Al:SrTiO(3) Particles upon High-Temperature Annealing, *ACS Appl. Mater. Interfaces*, 2023, **15**, 14990–15003, DOI: [10.1021/acsami.3c00250](https://doi.org/10.1021/acsami.3c00250).
- 25 B. Moss, *et al.*, Linking *in situ* charge accumulation to electronic structure in doped SrTiO<sub>3</sub> reveals design principles for hydrogen-evolving photocatalysts, *Nat. Mater.*, 2021, **20**, 511–517, DOI: [10.1038/s41563-020-00868-2](https://doi.org/10.1038/s41563-020-00868-2).
- 26 S. O'Donnell, *et al.*, Pushing the Limits of Metastability in Semiconducting Perovskite Oxides for Visible-Light-Driven Water Oxidation, *Chem. Mater.*, 2020, **32**, 3054–3064, DOI: [10.1021/acs.chemmater.0c00044](https://doi.org/10.1021/acs.chemmater.0c00044).
- 27 P. Makula, M. Pacia and W. Macyk, How To Correctly Determine the Band Gap Energy of Modified Semiconductor Photocatalysts Based on UV-Vis Spectra, *J. Phys. Chem. Lett.*, 2018, **9**, 6814–6817, DOI: [10.1021/acs.jpclett.8b02892](https://doi.org/10.1021/acs.jpclett.8b02892).
- 28 H. Onishi, Sodium Tantalate Photocatalysts Doped with Metal Cations: Why Are They Active for Water Splitting?, *ChemSusChem*, 2019, **12**, 1825–1834, DOI: [10.1002/cssc.201802935](https://doi.org/10.1002/cssc.201802935).
- 29 M. Pidburtnyi, B. Zanca, C. Coppex, S. Jimenez-Villegas and V. Thangadurai, A Review on Perovskite-Type LaFeO<sub>3</sub> Based Electrodes for CO<sub>2</sub> Reduction in Solid Oxide Electrolysis Cells: Current Understanding of Structure–Functional Property Relationships, *Chem. Mater.*, 2021, **33**, 4249–4268, DOI: [10.1021/acs.chemmater.1c00771](https://doi.org/10.1021/acs.chemmater.1c00771).
- 30 Q. Jia, A. Iwase and A. Kudo, BiVO<sub>4</sub>–Ru/SrTiO<sub>3</sub>:Rh composite Z-scheme photocatalyst for solar water splitting, *Chem. Sci.*, 2014, **5**, 1513–1519, DOI: [10.1039/c3sc52810c](https://doi.org/10.1039/c3sc52810c).
- 31 R. Asai, *et al.*, A visible light responsive rhodium and antimony-codoped SrTiO<sub>3</sub> powdered photocatalyst loaded with an IrO<sub>2</sub> cocatalyst for solar water splitting, *Chem. Commun.*, 2014, **50**, 2543–2546, DOI: [10.1039/c3cc49279f](https://doi.org/10.1039/c3cc49279f).
- 32 R. Shannon, Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides, *Acta Crystallogr., Sect. A*, 1976, **32**, 751–767, DOI: [10.1107/S0567739476001551](https://doi.org/10.1107/S0567739476001551).
- 33 Y. Yang, X. Ning, S. Luo, F. Dong and L. Li, Electron Irradiation Effects of SrZrO<sub>3</sub> Ceramic for Radioactive Strontium Immobilization, *Procedia Environ. Sci.*, 2016, **31**, 330–334, DOI: [10.1016/j.proenv.2016.02.044](https://doi.org/10.1016/j.proenv.2016.02.044).
- 34 H. Kato, M. Kobayashi, M. Hara and M. Kakihana, Fabrication of SrTiO<sub>3</sub> exposing characteristic facets using molten salt flux and improvement of photocatalytic activity for water splitting, *Catal. Sci. Technol.*, 2013, **3**, 1733–1738, DOI: [10.1039/c3cy00014a](https://doi.org/10.1039/c3cy00014a).
- 35 S. S. Arbuj, R. R. Hawaldar, S. Varma, S. B. Waghmode and B. N. Wani, Synthesis and Characterization of ATiO<sub>3</sub> (A = Ca, Sr and Ba) Perovskites and Their Photocatalytic Activity Under Solar Irradiation, *Sci. Adv. Mater.*, 2012, **4**, 568–572, DOI: [10.1166/sam.2012.1320](https://doi.org/10.1166/sam.2012.1320).
- 36 T. Takata and K. Domen, Defect Engineering of Photocatalysts by Doping of Aliovalent Metal Cations for Efficient Water Splitting, *J. Phys. Chem. C*, 2009, **113**, 19386–19388.
- 37 D. K. Bhat, H. Bantawal and U. S. Shenoy, Rhodium doping augments photocatalytic activity of barium titanate: effect of electronic structure engineering, *Nanoscale Adv.*, 2020, **2**, 5688–5698, DOI: [10.1039/d0na00702a](https://doi.org/10.1039/d0na00702a).
- 38 F. E. Osterloh, in *Integrated Solar Fuel Generators Energy and Environment Series*, 2018, vol. 214–280.
- 39 H. Sudrajat, *et al.*, Water-Splitting Activity of La-Doped NaTaO<sub>3</sub> Photocatalysts Sensitive to Spatial Distribution of Dopants, *J. Phys. Chem. C*, 2020, **124**, 15285–15294, DOI: [10.1021/acs.jpcc.0c03822](https://doi.org/10.1021/acs.jpcc.0c03822).
- 40 B. Zutter, *et al.*, Single-Particle Measurements Reveal the Origin of Low Solar-to-Hydrogen Efficiency of Rh-Doped SrTiO<sub>3</sub> Photocatalysts, *ACS Nano*, 2023, **17**(10), 9405–9414.



- 41 C. Shearer, J. Alvino, M. Batmunkh and G. Metha, Pt Nanocluster Co-Catalysts for Photocatalytic Water Splitting, *C*, 2018, **4**, 64, DOI: [10.3390/c4040064](https://doi.org/10.3390/c4040064).
- 42 H. Lyu, *et al.*, An Al-doped SrTiO<sub>3</sub> photocatalyst maintaining sunlight-driven overall water splitting activity for over 1000 h of constant illumination, *Chem. Sci.*, 2019, **10**, 3196–3201, DOI: [10.1039/c8sc05757e](https://doi.org/10.1039/c8sc05757e).
- 43 D. H. K. Murthy, *et al.*, Revealing the role of the Rh valence state, La doping level and Ru cocatalyst in determining the H<sub>2</sub> evolution efficiency in doped SrTiO<sub>3</sub> photocatalysts, *Sustainable Energy Fuels*, 2019, **3**, 208–218, DOI: [10.1039/c8se00487k](https://doi.org/10.1039/c8se00487k).

