### **Nanoscale**



PAPER View Article Online



Cite this: Nanoscale, 2025, 17, 16682

# Oxidation and recharge of reactive structural Fe( $\parallel$ ) in titanomagnetite (Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub>) nanoparticles†

D. V. Boglaienko, Da J. Liu, Db M. P. Prange, Da O. Qafoku, Da M. Sassi, Da E. Arenholz, Dc C. I. Pearce \* and K. M. Rosso \* talks and K. M. Rosso \* and K.

Mixed-valent iron oxide minerals, such as magnetite  $(Fe(|||)(Fe(||||))_2O_4)$ , are an important source of solidstate ferrous iron (Fe(II)) that can impact the speciation and transport of electron accepting contaminants in the Earth's subsurface, such as radioactive pertechnetate ( $^{99}$ Tc( $v_{\parallel}$ ) $O_4$  $^-$ ). However, when oxidizing conditions are encountered, structural Fe(II) at the mineral surface is consumed yielding a maghemite (γ-Fe(III)<sub>2</sub>O<sub>3</sub>)-like layer that limits further electron transfer. This oxidized surface layer can be recharged back to the original Fe(II)/(III) ratio by re-exposure to reducing conditions, i.e., aqueous solutions containing Fe<sup>2+</sup>. However, for substituted magnetite (Fe<sub>3-x</sub> $M_xO_4$ , M = transition metal cation), the extent of this redox recyclability is unclear. Here, we examine oxidation and recharge for titanomagnetite ( $Fe_{3-x}Ti_xO_4$ ) nanoparticles, where the Fe(II)/Fe(III) ratio varies by the amount of Fe(II) required to charge balance the titanium (Ti(ıv)) substituted into the structure. The nanoparticles were synthesized by aqueous precipitation from a solution containing ferrous, ferric and titanium chloride at room temperature. Transmission electron microscopy combined with electron energy loss spectroscopy revealed that rapid precipitation formed core-shell-like nanoparticles consisting of a hyperstoichiometric magnetite core, with Ti(IV) and charge balancing Fe(II) enriched at the surface. This surface enrichment made Fe(II) more available for electron transfer reactions with redox active solution species. Examination of oxidation by  $H_2O_2$  followed by recharge with aqueous Fe<sup>2+</sup> indicates recyclability of reducing equivalents in the nanoparticles, yielding a core recrystallized to stoichiometric magnetite and a shell bearing excess Fe(II) to charge balance the substituted Ti(iv). The recharged particles are shown to have restored redox reactivity with 99Tc(vii)O<sub>4</sub> resulting in reduction to  $^{99}$ Tc(IV)O<sub>2</sub> and oxidation of the structural Fe(III) to Fe(III).

Received 7th March 2025, Accepted 12th June 2025 DOI: 10.1039/d5nr00989h

rsc.li/nanoscale

### 1. Introduction

Iron redox cycling, entailing alternation between  $Fe^{3+}$  and  $Fe^{2+}$  valence states, is a common process in natural environments such as rooting zones, soils, and near-shore environments.<sup>1</sup> Cycling caused by episodic oxygen  $(O_2)$  depletion during rainfall, soil inundation and organic matter leaching changes the biogeochemical conditions. Iron  $(Fe^{3+}, Fe^{2+})$  and titanium  $(Ti^{4+})$  belong to major elements of soil originating from terrestrial basalts.<sup>2</sup> They are present in a variety of Ti-substituted iron oxides that tend to be chemically resistant to weathering, particularly as their crystallinity increases with multiple redox oscillations.<sup>1,3</sup>

The end member magnetite (Fe<sub>3</sub>O<sub>4</sub>) is a common iron mineral in basalts and associated soils. It has an inverse spinel structure (Fe<sup>3+</sup>)<sub>A</sub>(Fe<sup>2+</sup>Fe<sup>3+</sup>)<sub>B</sub>O<sub>4</sub>, where A and B refer to tetrahedral and octahedral sites, respectively. In sediments originating from basalt, transition metals, such as Ti<sup>4+</sup>, often substitute for Fe in the magnetite structure to form titanomagnetite (Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub>). Ti(IV) replaces Fe(III) in octahedral (B) sites and causes reduction of remaining structural Fe(III) to Fe(II) for charge balance, increasing the solid-state Fe(II)/Fe(III) ratio (>0.5) compared to pure magnetite (Fe( $\pi$ )/Fe( $\pi$ ) = 0.5). Here, the end member is ulvöspinel ( $Fe_{3-x}Ti_xO_4$ , x = 1),  $Fe_2TiO_4$ , or  $(Fe(II))_A(Fe(II))_B(Ti(IV))_BO_4$ , where x defines the amount of Ti in the solid solution. At low x,  $Fe(\pi)$  tends to occupy the octahedral sublattice; with increasing x the distribution of  $Fe(\pi)$ and Fe(III) between A and B sites changes, impacting the magnetic, electronic, and structural properties. 5-8 The Fe(II)/Fe(III) ratio in titanomagnetites is affected not only by x, but also by the extent of oxidation. The oxidation of titanomagnetite is a topotactic reaction involving loss of iron from the structure to produce titanomaghemite,  $Fe_{2-2x+\frac{2}{3}y}^{(III)}Fe_{1+x-y}^{(II)}Ti_x^{(IV)}\frac{y}{3}E_4^{(II-)}$ , where yis the oxidation parameter that varies from 0, unoxidized, to 1,

<sup>&</sup>lt;sup>a</sup>Pacific Northwest National Laboratory, Richland, WA 99352, USA.
E-mail: carolyn.pearce@pnnl.gov; Fax: +1509 376 3650; Tel: +1 509 371 6380

<sup>b</sup>College of Environmental Sciences and Engineering, Peking University, Beijing, 100871. China

<sup>&</sup>lt;sup>c</sup>Brookhaven National Laboratory, National Synchrotron Light Source II, Upton, NY 11973 USA

<sup>†</sup>Electronic supplementary information (ESI) available. See DOI: https://doi.org/ 10.1039/d5nr00989h

Nanoscale Paper

oxidized; and symbol  $\square$  represents cationic site vacancies. <sup>9,10</sup> The interfacial reaction of titanomagnetites with redox active contaminants in solution is of interest for predicting the potential of these phases to transform the speciation of key metals or organics in soils and sediments.

The reduction of contaminants by titanomagnetite has been investigated in a limited number of previous studies. Marsac et al. (2017)<sup>11</sup> compared the redox activity of titanomagnetite with that of Fe(II)-amended magnetite for the reduction of nitroaromatic compounds. This work confirmed that Fe(II) recharge of magnetite to an equivalent amount of total Fe(II) as in titanomagnetite resulted in higher reduction rate, but did not investigate Fe(II) recharge of titanomagnetite. Latta et al., (2013)12 studied the reaction between aqueous hexavalent uranium (U<sup>6+</sup>), as uranyl acetate, and titanomagnetite nanoparticles. They demonstrate that titanomagnetites reduced U6+ to sorbed U(1v), in contrast to magnetite that reduced  $U^{6+}$  to uraninite  $(U(IV)O_2)$ . They varied the Fe(II)/Fe(III)ratio by oxidizing the structural Fe(II) with hydrogen peroxide and showed that redox reactivity was controlled by the Fe(II)/Fe (III) ratio. Wylie et al. (2016)<sup>13</sup> investigated the effect of titanomagnetite on hexavalent neptunium (Np6+) sorption and speciation and showed that increasing Ti concentration resulted in a greater extent of reduction to sorbed Np(IV). All of these studies report direct relationship between redox reactivity and Fe(II)/Fe(III) ratio controlled by Ti(IV) content. Here, we investigate the reaction of titanomagnetites with technetium-99 as pertechnetate (99Tc(vII)O<sub>4</sub> (aq), hereafter referred to as TcO<sub>4</sub>), a highly soluble radioactive contaminant present in the subsurface beneath nuclear reprocessing facilities. This reaction has been studied for its prospect of immobilizing TcO<sub>4</sub> as the reduced and less soluble Tc(IV)O2·nH2O on the titanomagnetite surface. 10 Liu et al. (2012) 10 showed that the kinetics of TcO<sub>4</sub> reduction by ~10 nm Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles had a positive correlation with Ti content and corresponding solid state Fe(II)/Fe(III) ratio. The mechanism of TcO<sub>4</sub><sup>-</sup> reduction involves the migration of structural Fe(II) to the surface of nanoparticles, where it reduces the TcO<sub>4</sub> and is oxidized to Fe(III), a process that continues to maintain Fe(II)/Fe(III) equilibrium at the nanoparticle surface. 10 A similar phenomenon has been shown for perrhenate (Re(vII)O<sub>4</sub><sup>-</sup>) reduction by magnetite nanoparticles. 14 This continued resupply of reducing equivalents from the interior to the nanoparticle surface differs from the classical understanding of magnetite reactivity established primarily through macroscopic bulk magnetite studies where oxidation through reaction with a redox active aqueous species, e.g., chromate (Cr(v<sub>I</sub>)O<sub>4</sub><sup>2-</sup>), leads to passivation of the magnetite surface. 15 Scaria et al. (2025) investigated the effect of magnetite stoichiometry (Fe(II)/Fe(III)) on Cr(VI)  $O_4^{2-}$  reduction and Cr(m) surface speciation. The study showed the formation of a spinel-type structure  $(Fe(II)Cr(III)_x)$  $Fe(III)_{2-x}O_4$ ) on stoichiometric magnetite, while the previously characterized tridentate trinuclear surface complex<sup>17</sup> was found only on oxidized magnetite, challenging the conventional understanding that Cr(III) primarily exists as precipitated (hydr)oxides.

In the subsurface, fluctuating water levels lead to varying oxygen penetration depths and therefore redox conditions change from oxidizing to reducing at low and high water levels, respectively. Previous work on oxidized magnetite showed that contact with aqueous Fe2+ under reducing conditions can restore stoichiometry, presumably by diffusion of adsorbed Fe2+ into the solid phase (via electron transfer and reduction of octahedral Fe(III) to Fe(II) and recrystallization at the surface without formation of secondary Fe(II)-bearing precipitates. 18,19 Byrne et al. (2015; 2016)20,21 showed that magnetite can also act as a recyclable electron donor and acceptor for phototrophic Fe(II)-oxidizing and Fe(III)-reducing bacteria, respectively, with microbial Fe(II) oxidation occurring at the mineral surface, and microbial Fe(III) reduction proceeding via electron conduction into the interior. The rechargeability of Fe(II) electron equivalents in titanomagnetite upon re-exposure to reducing conditions is an important remaining question. Therefore, the present study examines the rechargeability of titanomagnetite (Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub>) nanoparticles with different initial Fe(II)/Fe(III) ratios controlled by the content of Ti (x = 0.00, 0.15 and 0.38), subjected to peroxide  $(H_2O_2)$  oxidation followed by recharge with Fe<sup>2+</sup>-containing solutions. The effects of nanoparticle oxidation and recharge on reactivity with respect to TcO<sub>4</sub> reduction is also investigated. Multimodal solid characterization techniques including surface sensitive Fe L-edge X-ray magnetic circular dichroism (XMCD), micro-Xray diffraction (μ-XRD) and transmission electron microscopy (TEM), were used to elucidate the effect of Ti content on the rechargeability of the oxidized nanoparticles and their subsequent reactivity with TcO<sub>4</sub><sup>-</sup>.

### 2. Materials and methods

#### 2.1 Synthesis

 $Fe_{3-x}Ti_xO_4$  nanoparticles were synthesized as described in the literature, <sup>8,10</sup> which involves instant precipitation through forced base hydrolysis according to eqn (1):

$$(1+x)Fe^{2+} + (2-2x)Fe^{3+} + xTi^{4+} + 8OH^{-}$$

$$\rightarrow Fe_{2-x}Ti_{x}O_{4} + 4H_{2}O$$
(1)

The nanoparticles were synthesized in a nitrogen-filled glovebox from a stoichiometric mixture of ferrous chloride (FeCl<sub>2</sub>), ferric chloride (FeCl<sub>3</sub>) and titanium chloride (TiCl<sub>4</sub>), dissolved in 0.3 M hydrochloric acid (HCl, pH < 1), and introduced into a 25% w/v ammonium hydroxide (NH<sub>4</sub>OH) solution with continuous stirring. The nanoparticles were magnetically separated, washed, and resuspended in deionized water (DIW), where they naturally equilibrated to a solution pH of  $\sim$ 8.5.

### 2.2. Wet chemical experiments

The conditions for the wet chemical experiments have been described in Liu *et al.* (2012).<sup>10</sup>

**2.2.1.** Nanoparticle oxidation.  $Fe_{3-x}Ti_xO_4$  (x = 0.00, 0.15 and 0.38) nanoparticles were prepared as in section 2.1 and

left stirring in the synthesis suspension (200 mL) at 500 rpm overnight. The synthesis suspension was then split into 4 batches of 50 mL, one batch was kept as the unoxidized material and sufficient hydrogen peroxide solution (30 wt%) was added to the other batches to oxidize 25% (0.063 for x = 0.00, 0.0725 mL for x = 0.15, and 0.085 for x = 0.38), 50% (0.162 for x = 0.00, 0.145 mL for x = 0.15, and 0.17 for x = 0.38)and in excess of 100% (1.62 for x = 0.00, 1.45 mL for x = 0.15, and 1.7 for x = 0.38) of the Fe(II) according to the equation:

$$2Fe(II) + H_2O_2 + 2H^+ \rightarrow 2Fe(III) + 2H_2O.$$
 (2)

The suspensions were left to equilibrate in the H<sub>2</sub>O<sub>2</sub> solution overnight with stirring at 500 rpm. For all batches, the resultant suspension was centrifuged and washed twice with DIW under ultrasonication for 5 min, followed by centrifugation at 3500 rpm for 5 min and resuspension in sufficient DIW to produce the initial suspension volume (50 mL).

2.2.2. Nanoparticle recharge with Fe<sup>2+</sup>. Known volumes of oxidized nanoparticle suspensions were added to glass serum bottles containing 20 mL pH 8 HEPES solution (30 mM) to give a concentration of 0.5 g L<sup>-1</sup> Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub>. FeCl<sub>2</sub>·4H<sub>2</sub>O solution (5 mM) in 0.5 M HCl was added to the bottles to give a final Fe<sup>2+</sup> concentration in solution of 0.05 mmol, 1 mmol or 2.5 mmol. The bottles were continuously shaken at 150 rpm for the duration of the experiment. For sampling, aliquots of suspension (1.5 mL) were transferred into Eppendorf centrifuge tubes and centrifuged for 5 min at 30 000 rpm. The concentration of Fe<sup>2+</sup> in the supernatant was analyzed by ferrozine assay (described in section 2.3). A solution of known Fe<sup>2+</sup> concentration was prepared as an external standard and analyzed using the same procedure as for the nanoparticle suspensions, to detect any oxidation or adsorption of aqueous Fe<sup>2+</sup> during the experiment. All experiments were performed in triplicate.

2.2.3.  $TcO_4^-$  reduction experiments. Caution! <sup>99</sup>Tc is a  $\beta^$ emitter with energy 0.29 MeV.<sup>22</sup> Experiments were conducted at a nonreactor nuclear facility by trained personnel.

TcO<sub>4</sub> reduction experiments were carried out in 30 mL glass serum bottles equipped with rubber stoppers and crimp seals. A suspension of solid to solution ratio of 1.3 mg: 30 mL was prepared by adding HEPES buffer to nanoparticles. The sealed bottles were shaken for 20 hours. A 5 mM <sup>99</sup>Tc stock solution was made by diluting NH4TcO4 (PerkinElmer Life Science Inc., Boston, MA) in DIW. After the 20-hour equilibration period, the suspension of nanoparticles was spiked with TcO<sub>4</sub> solution targeting concentration of 10 μM, which was continuously shaken and sampled over time in triplicate. Suspension aliquots (3 mL) were filtered with a 0.1 µm syringe filter, and the 1 mL filtrate was added to 9 mL of scintillation cocktail in the glovebox to be counted utilizing a Packard 2500TR liquid scintillation counter (Packard Instrument Co. Meriden, CT) for 10 min. The HEPES buffer solution without TcO<sub>4</sub> was used for background subtraction, and the concentration of <sup>99</sup>Tc in solution was calculated in dpm mL<sup>-1</sup>.

Control experiments were conducted to test for potential TcO<sub>4</sub> adsorption onto the glass bottles and the syringe filters.

TcO<sub>4</sub><sup>-</sup> solution (1 μM) was spiked into HEPES solution (50 mL) in a glass bottle and shaken for five days. The final TcO<sub>4</sub> concentration decreased less than 3%. TcO<sub>4</sub> solution (1 μM) was also filtered through the 0.1 µm syringe filters used in the reduction experiments. The TcO4- concentration decreased  $\sim 3.3\%$  after filtration. Thus, the effect of  $TcO_4$  adsorption by the glass serum bottles and the syringe filters was minimal.

#### 2.3. Characterization

Chemical analysis was used to determine the total chemical composition of the nanoparticles (Fe(II), total Fe, and Ti content) by digesting samples in N<sub>2</sub>-sparged 5 M HCl inside the glovebox with shaking overnight. The ferrozine method was used to determine the concentration of Fe<sup>2+</sup> in solution.<sup>23</sup> Ferrozine reagent (1.8 mL, 1 g L<sup>-1</sup> ferrozine in 50 mM HEPES buffer, pH 7.0) was added to the diluted acid digest solution (0.2 mL), and the absorbance at 562 nm was measured using a Shimadzu UV-2501 PC spectrophotometer. A calibration curve of the absorbance at 562 nm for solutions of known Fe<sup>2+</sup> concentration was used to determine the Fe2+ concentration in solution. Total Fe and Ti concentrations were determined by adding 0.05 mL of the digested nanoparticles to 4.95 mL 2% HNO<sub>3</sub> and analyzing the solutions using inductively coupled plasma - mass spectrometry (ICP-MS) with an Agilent 7500 instrument.

A Jeol-JEM 2010 transmission electron microscope (TEM), equipped with a LaB6 filament and a post-column Gatan Image Filter (GIF2000) at an acceleration voltage of 200 kV and point-to-point resolution of 0.2 nm was used to determine particle size and morphology. Scanning TEM (STEM) was combined with electron energy loss spectroscopy (EELS), with energy dispersion of 0.25 eV per pixel, to map the chemistry of the nanoparticles. Images were recorded with a slow-scan charge-coupled device (CCD) camera and processed with Digital Micrograph (Gatan, USA). Samples for TEM analysis were prepared by dipping a 400 mesh copper grid coated with lacey carbon film into a diluted nanoparticle suspension and drying it inside an N2-filled glovebox. Samples were taken out of the glovebox directly before measurement.

For micro-X-ray diffraction (μ-XRD) measurements to characterize nanoparticle suspensions in situ, boron-rich capillary tubes (0.5 mm outer diameter, Charles Supper Company) were loaded with the anaerobic aqueous nanoparticle suspensions, sealed with wax (Charles Supper Company), and kept in the glovebox until immediately prior to measurement. A Rigaku D/Max Rapid II instrument with a 2D image plate detector, equipped with a MicroMax 007HF generator and a rotating chromium anode ( $\lambda = 2.2897 \text{ Å}$ ) was used for  $\mu$ -XRD measurements. It was focused on a capillary tube using a 30 µm diameter collimator. The diffraction rings were integrated with 2DP, Rigaku 2D Data Processing Software (Ver. 1.0, Rigaku, 2007). JADE 8.5 from Materials Data Inc. and the PDF4+ database from ICSD were used for the analysis of diffraction data. A cubic spline function was used to fit the background, and a pseudo-Voigt profile shape function was applied to the diffraction peaks. The cubic cell parameter and crystalNanoscale Paper

lite particle size were determined using a cubic magnetite ( $Fe_3O_4$ ) structure (PDF # 00-019-0629) in JADE; and the cell parameter of a Si standard (Silicon powder, NIST 640c) was measured to verify the sample-to-detector distance (deviation of the observed cell parameter from the standard was 0.002 Å).

X-ray absorption (XA) spectra at the Fe L2.3 edges were obtained at the Advanced Light Source (ALS), Berkeley, CA, on the beamline 4.0.2, employing the eight-pole resistive magnet end-station,<sup>24</sup> and collected in the total-electron yield (TEY) mode with an effective probing depth of 50 Å.<sup>25</sup> Aliquots of the anaerobic nanoparticle suspensions were deposited onto carbon tape attached to the copper sample holder and dried in the N2-filled glovebox. The sample holder was then sealed into an anaerobic container for shipment to ALS. The sample holder was removed from the anaerobic container immediately prior to insertion into the N2-filled end-station at beamline 4.0.2. XA spectra were collected from 609 to 740 eV for two opposite magnetization directions, reversing the applied 0.6 T field at each energy point. The X-ray magnetic circular dichroism (XMCD) spectrum was obtained as the difference between two XA spectra normalized to the incident beam intensity.<sup>26</sup> To calculate Fe(II) and Fe(III) distribution over tetrahedral and octahedral sites, the XMCD spectra were fit using a nonlinear least-squares analysis based on ligand field multiplet models, 27,28 which simulate the effects of crystal field on the atomic energy levels and take into account the symmetry of the local environment and charge transfer effects. In these calculations, the 10Dq crystal field parameters were taken as 1.2 and 0.6 eV for Fe cations in octahedral and tetrahedral sites. The results were convoluted using a Gaussian of  $\sigma = 0.2$  eV to account for instrumental broadening and using a Lorentzian of  $\Gamma = 0.3$  (0.5) eV for the L<sub>3</sub> (L<sub>2</sub>) edge to account for intrinsic core-hole lifetime broadening. The Ti L2,3 XAS data (not sensitive to the magnetic field) were collected on the same beamline 4.0.2 at the ALS. For the ligand field multiplet model fitting, the estimated random error per cation site occupancy value for the XMCD-derived Fe(II)/Fe(III) ratio is  $\pm 0.02$ .<sup>29</sup>

Fe K-edge and Ti K-edge XANES and EXAFS measurements were made at 20-BM at the Advanced Photon Source (APS), Argonne, IL. A Si (1 1 1) monochromator was used with a 1 mm entrance slit located approximately 50 m from the source. The monochromator allowed an energy resolution of about 1 eV at the Fe edge and 0.7 eV at the Ti edge. Samples of nanoparticle suspension were transferred in the glovebox into Teflon holders with Kapton windows and flash frozen in liquid  $N_2$  for shipment. At the beamline, nanoparticle samples were measured at 17 K to avoid oxidation. Data were taken in transmission mode with a Fe foil used for online energy calibration. The XANES data were analyzed using the Athena interface to the IFEFFIT program package.  $^{30}$ 

### 2.4. Theoretical modeling of Fe K-edge and Ti K-edge EXAFS

Local structures for Ti atoms were obtained by replacing one or two Fe atoms in the magnetite structure<sup>31</sup> with Ti in density functional theory structural relaxations using a PBE+U theory in which the PBE exchange correlation approximation<sup>32</sup> is aug-

mented with an on-site Coulomb repulsion of U - J = 4 eV for the Fe d orbitals following Dudarev et al. (1998).<sup>33</sup> No Hubbard corrections were used for Ti. The VASP code<sup>34</sup> and associated projector-augmented wave datasets<sup>35</sup> were used to compute the Kohn-Sham orbitals on a  $4 \times 4 \times 4$  grid of k-points in a basis of plane waves defined by an energy cutoff of 400 eV. Although magnetite is ferrimagnetic, spin-polarized simulations were performed in a ferromagnetic configuration with a constrained total moment to prevent the collapse of the high-spin configuration of the Fe(II) sites in the structurally disordered model during the relaxations. Simulations of XA spectra were made using the FEFF code<sup>36</sup> to evaluate the path expansion in clusters generated from the relaxed structures. Overlapped atomic potentials,  $R_{\text{max}} = 4.36 \text{ Å}$ , and otherwise default settings were used. A uniform thermal disorder parameter  $\sigma^2 = 0.01 \text{ Å}^2$  was applied to all paths.

### 3. Results and discussion

# 3.1 Characterization of as-synthesized titanomagnetite nanoparticles

The as-synthesized titanomagnetite nanoparticles used in this study were synthesized and characterized as described in Pearce *et al.* (2012)<sup>8</sup> and Liu *et al.* (2012).<sup>10</sup> The nanoparticles were characterized by chemical analysis of digested nanoparticles (ferrozine method for UV-vis spectroscopy for Fe<sup>2+</sup> and ICP-MS for total Fe and Ti), TEM (particle size),  $\mu$ -XRD (cell parameter and Fe( $\pi$ )/Fe( $\pi$ ) ratio), XAS and XMCD (Fe( $\pi$ )/Fe( $\pi$ ) ratio) and XANES and EXAFS (local coordination environment). The characteristics of the as-synthesized titanomagnetite nanoparticles are summarized in Table 1, as originally reported in Pearce *et al.* (2012).<sup>8</sup> The nanoparticles had near spherical shape with an equivalent diameter of 9.4–10.6 nm (±2 nm) (Fig. 1A).

Fe L-edge XAS in TEY mode and XMCD analyses provide surface sensitive information, down to 50 Å, and the signal strength decreases exponentially with depth. The XMCD signal is sensitive to the oxidation state and local structure of magnetically ordered iron cations at solid surfaces. It is derived from the difference of two XA spectra obtained with circularly polarized light in alternating opposing static applied magnetic fields. Fe(II)/Fe(III) ratios at nanoparticle surfaces were estimated by fitting the Fe L-edge XMCD spectra with weighted sums of the theoretically calculated spectra for Fe octahedral and tetrahedral sites. Specifically calculated spectra for Fe octahedral and tetrahedral sites. The methods based on multireference configuration interaction (MRCI) calculations and ligand-field multiplet models were also used to analyze the XMCD data, and the results were consistent

Table 1 Characteristics of the as-synthesized titanomagnetite nanoparticles<sup>8</sup>

x	Size (nm)	Cell parameter (Å)		Fe(III) (mmol g <sup>-1</sup> )	Ti(IV) (mmol g <sup>-1</sup> )	Composition (experimental)	Composition (theoretical)	( ) ( )	$Fe(II)/Fe(III)$ $XMCD \pm 0.02^{a}$
0.15	9.4	8.406 8.415 8.429	4.42 4.44 4.76	7.89 6.33 5.02	0.00 0.55 1.38	$\begin{split} &Fe(\pi)_{1.08}Fe(\pi)_{1.92}O_4 \\ &Fe(\pi)_{1.17}Fe(\pi)_{1.68}Ti_{0.15}O_4Fe(\pi)_{1.27}Fe(\pi)_{1.35}Ti_{0.38}O_4 \end{split}$	$\begin{aligned} & Fe(\pi)_{1,100}Fe(\pi)_{2,00}O_4 \\ & Fe(\pi)_{1,15}Fe(\pi)_{1,70}Ti_{0,15}O_4Fe(\pi)_{1,38}Fe(\pi)_{1,24}Ti_{0,38}O_4 \end{aligned}$	0.556 0.656 0.829	0.604 0.667 0.878

<sup>&</sup>lt;sup>a</sup> Estimated according to Coker et al. (2009).<sup>29</sup>

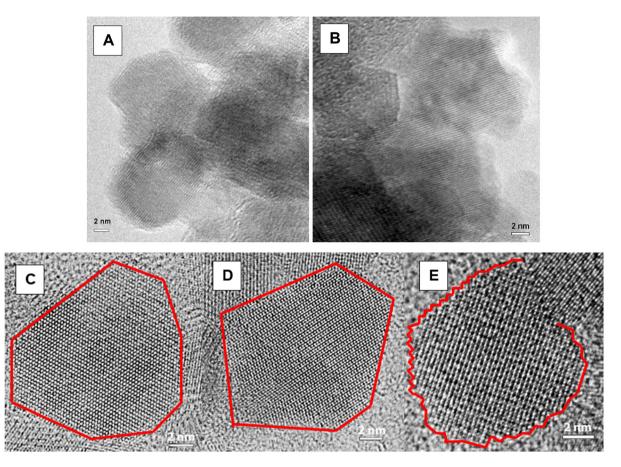


Fig. 1 TEM of x = 0.15 (A) before and (B) after oxidation with  $H_2O_2$ ; (C) x = 0.15 as-synthesized, euhedral with straight edges, with a diameter of  $\sim$ 9.5 nm; (D) x = 0.15 oxidized, euhedral with straight edges and a diameter of  $\sim$ 8.8 nm; (E) x = 0.15 recharged, rounded, rough edges, with a diameter of  $\sim$ 9.6 nm.

between the models regarding the trends of the Fe(II)/Fe(III) ratios. Data summarized in Table 1 show that the surface Fe (II)/Fe(III) ratio is similar to the bulk Fe(II)/Fe(III) ratio, obtained from the relationship between Fe(II)/Fe(III) ratio and cell parameters from XRD, for the as-synthesized nanoparticles.

### 3.2 Oxidation of titanomagnetite nanoparticles

The amount of  $\rm H_2O_2$  required to oxidize the  $\rm Fe_{3-x}Ti_xO_4$  nanoparticle suspensions to different extents (25%, 50%, and added in excess for 100%) was calculated based on the extent of Ti substitution (x), i.e. 0.063 mL, 0.162 mL, and 1.62 mL for x=0.00; 0.0725 mL, 0.145 mL, and 1.45 mL for x=0.15; 0.085 mL, 0.17 mL, and 1.7 mL for x=0.38. The pH of the suspensions was ~8.5 and, under these slightly alkaline con-

ditions,  $H_2O_2$  underwent disproportionation to produce oxygen gas, as evidenced by the formation of bubbles in the suspensions, according to eqn (3):

$$2H_2O_2 \rightarrow 2H_2O + O_2 \tag{3}$$

The nanoparticle suspensions changed color from black to brown, indicating oxidation of Fe(II) to Fe(III) by both  $H_2O_2$  and  $O_2$ . After equilibration in the presence of  $H_2O_2$  overnight, the nanoparticles were washed to remove any excess  $H_2O_2$  and resuspended in DIW. Qualitative examination of the particles using TEM revealed that oxidation did not significantly change the particle shape or surface structure (Fig. 1B), as also observed in studies by Jungcharoen *et al.* (2021)<sup>18</sup> and Demangeat *et al.* (2018).<sup>43</sup> Fig. 1A and B show representative

Nanoscale

particles from the x = 0.15 sample, before and after oxidation, respectively. The euhedral particles were similar in size (~9 nm in equivalent diameter), and exhibited atomically flat, common cubic faces.

While the amounts of Fe(II) (mmol g<sup>-1</sup>) measured by acid digestion and ferrozine assay were similar to the Fe(II) (mmol g<sup>-1</sup>) calculated from XRD data for the as-synthesized samples, the amounts measured by digestion for the H2O2 oxidized samples were substantially lower than the amounts calculated from the XRD data, and the amounts measured by digestion for the Fe<sup>2+</sup> reduced samples were substantially higher than the amount calculated from the XRD data, for most of the samples (Table 2). Possibly, the results were impacted by some residual H<sub>2</sub>O<sub>2</sub> and Fe<sup>2+</sup>, despite replacing the solution with water, that is why the Fe(II)/Fe(III) ratio determined by chemical digestion was not included in Table 2.

The nanoparticles were also measured under anaerobic conditions and in aqueous suspension using capillary µ-XRD before and after exposure to H2O2 to determine the effect of oxidation on the crystal structure of the nanoparticles. The background subtracted diffraction patterns for x = 0.15 nanoparticles before and after reaction with different concentrations of H<sub>2</sub>O<sub>2</sub> (Fig. S1†) show that no new phases were produced, and the only peaks present corresponded to titanomagnetite. A shift of peak position towards higher two-theta values after exposure to increasing concentrations of H2O2 was observed with all values of x, demonstrating a decrease of unit cell parameter. These observations are consistent with the previously published studies on this material.8,10

Due to the systematic relationship between unit-cell parameter and Fe(II)/Fe(III) ratio in these phases, defined as the "Master Curve" in Pearce et al. (2012),8 the change in Fe(II)/ Fe(III) ratio in the Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles because of oxidation with H2O2 could be determined. The unit cell parameter was obtained using whole pattern fitting and Rietveld refinement which also provided crystallite particle size. The unit cell parameters, derived Fe(II)/Fe(III) ratios and particle size for the  $Fe_{3-x}Ti_xO_4$  (x = 0.00, 0.15 and 0.38) nanoparticles, before (samples with 0 mL of H2O2) and after oxidation (variable volumes of H2O2 depending on the extent of Ti substitution) are given in Table 2. Oxidation at each value of x led to slight decrease in crystallite particle size due to: (i) contraction of the lattice due to the presence of larger amounts of the smaller Fe(III) cation; and (ii) removal of Fe from the structure through dissolution (Table 2). Fig. 2A shows the change in XRD-derived Fe(II)/Fe(III) ratio, as a function of x, with different concentrations of H<sub>2</sub>O<sub>2</sub>. The initial Fe(II)/Fe(III) ratio increased with x (expected due to charge balance for Ti(v) in the lattice) and resulted in a greater potential for oxidation, as shown by the increasing impact of the different H<sub>2</sub>O<sub>2</sub> concentrations on the extent of oxidation in the  $Fe_{3-x}Ti_xO_4$  nanoparticles. There was, however, a limit to the extent of oxidation under these conditions, as shown by the relatively small change in Fe(II)/Fe (III) ratio for the most oxidized samples, despite exposure to 10 times higher concentration of H2O2. Jungcharoen et al. (2022)<sup>44</sup> investigated magnetite oxidation under different pH and redox conditions and also found that 100% oxidation was not achievable. This suggests that the extent of oxidation is controlled by the solid-state characteristics of the particles and not by the concentration of H2O2 in solution. The physical limit on the extent of oxidation of titanomagnetites (x > 0.00), representing the Fe(II) that must remain in the Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> structure to balance the Ti(IV), is shown as the dashed line in Fig. 2.9 Only the most oxidized x = 0.38 sample approaches this physical limit (Fig. 2A) suggesting higher availability of structural Fe(II). Worm and Banerjee (1984)9 experimentally demonstrated migration of Fe(II) out of the lattice with oxidation of titanomagnetite; here, higher substitution of Ti(IV)

Table 2 Characteristics of the nanoparticles before oxidation, after oxidation and recharge

Sample	Fe(II) (mmol g <sup>-1</sup> ) Chem.	Fe(II) (mmol g <sup>-1</sup> ) XRD	Fe(II)/Fe(III) XRD ± 0.05	Fe(II)/Fe(III) XMCD ± 0.02	Particle Size (nm)	Ti/Fe Chem.	Ti/Fe XAS
x = 0.00							
Before oxidation	4.42	4.64	0.556	0.604	10.2	0.0	0.0
Oxidation with 0.063 mL of H <sub>2</sub> O <sub>2</sub>	2.42	3.11	0.320	0.447	9.6	0.0	0.0
Recharge with 0.05 mmol g <sup>-1</sup> Fe <sup>2+</sup>	7.52	4.37	0.509	0.630	10.6	0.0	0.0
Oxidation with 0.162 mL of H <sub>2</sub> O <sub>2</sub>	2.24	3.25	0.339	0.493	9.3	0.0	0.0
Oxidation with 1.62 mL of H <sub>2</sub> O <sub>2</sub>	0.92	2.76	0.274	0.382	9.2	0.0	0.0
Recharge with 2.5 mmol $g^{-1}$ Fe <sup><math>\overline{2}</math>+</sup>	5.35	4.25	0.489	0.523	10.6	0.0	0.0
x = 0.15							
Before oxidation	4.44	4.90	0.656	0.667	9.5	0.045	0.049
Oxidation with 0.0725 mL of H <sub>2</sub> O <sub>2</sub>	1.71	3.25	0.364	0.552	9.0	0.047	0.055
Recharge with 0.05 mmol g <sup>-1</sup> Fe <sup>2+</sup>	5.20	4.34	0.526	0.638	9.9	0.033	0.043
Oxidation with 0.145 mL of H <sub>2</sub> O <sub>2</sub>	1.11	2.35	0.241	0.425	8.9	0.047	0.035
Recharge with 2.5 mmol g <sup>-1</sup> Fe <sup>2+</sup>	4.34	4.18	0.516	0.625	10.4	0.032	0.031
Oxidation with 1.45 mL of H <sub>2</sub> O <sub>2</sub>	1.31	2.54	0.266	0.411	8.6	0.046	0.050
x = 0.38							
Before oxidation	4.76	5.14	0.829	0.878	10.7	0.133	0.120
Oxidation with 0.085 mL of H <sub>2</sub> O <sub>2</sub>	2.10	2.98	0.368	0.690	10.6	0.120	0.104
Recharge with 0.05 mmol g <sup>-1</sup> Fe <sup>2+</sup>	5.01	4.02	0.561	0.800	12.0	0.084	0.117
Oxidation with 0.17 mL of H <sub>2</sub> O <sub>2</sub>	0.73	2.03	0.228	0.526	10.6	0.118	0.085
Recharge with 2.5 mmol $g^{-1}$ Fe <sup><math>\overline{2}</math>+</sup>	3.66	4.02	0.561	0.735	11.6	0.086	0.090
Oxidation with 1.7 mL of H <sub>2</sub> O <sub>2</sub>	0.51	2.16	0.246	0.500	10.0	0.130	0.072

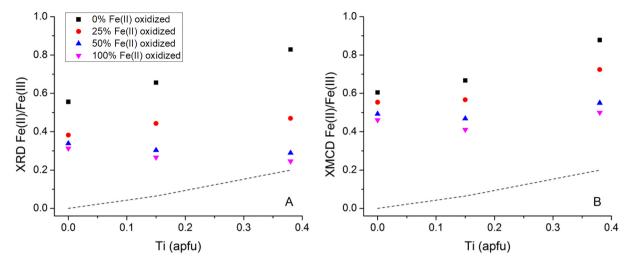


Fig. 2 Change in (A) XRD-derived Fe(ii)/Fe(iii) ratio and (B) XMCD-derived Fe(ii)/Fe(iii) ratio, as a function of x, with a theoretical 0%, 25%, 50%, and 100% of the Fe(ii) oxidized using different concentrations of  $H_2O_2$  (exact volumes of  $H_2O_2$  used are provided in Table 2). The dashed line represents the  $Fe^{2+}$  in the  $Fe_{3-x}Ti_xO_4$  structure to charge balance Ti(iv) (Worm and Banerjee, 1984).

into magnetite, x, resulted in higher mobilization of the structural Fe( $\pi$ ).

The  $Fe_{3-x}Ti_xO_4$  (x = 0.00, 0.15 and 0.38) nanoparticles before and after reaction with H<sub>2</sub>O<sub>2</sub> were also analyzed using XA (total Fe and Ti) and XMCD (magnetic component of the sample) at the Fe L2.3-edge and the Ti L2.3-edge. The XA and XMCD spectra for x = 0.15 nanoparticles before and after reaction with different concentrations of H2O2 are shown in Fig. 3A and B respectively. The L<sub>2,3</sub>-edge for Fe shifts to higher energy if oxidation state increases.<sup>45</sup> In Fig. 3A, the overall peak intensity has been normalized to one and the lower energy Fe L2,3-edge peak at 707.8 eV decreases with exposure to increasing H<sub>2</sub>O<sub>2</sub> concentrations, due to oxidation. Measured XMCD spectra for the nanoparticles have three main peaks: octahedral Fe(II) (negative peak at ~708 eV), tetrahedral Fe(III) (positive peak at ~709.5 eV), and octahedral Fe(III) (negative peak at ~710.5 eV). According to calculated spectra for these three main components in magnetite, the experimental XMCD spectrum can be fit to produce occupancy ratios for the proportions of Fe(II) and Fe(III) in the octahedral site, and of Fe(III) in the tetrahedral site. The Fe(II)/Fe(III) ratios for titanomagnetite nanoparticles before and after oxidation, calculated from the XMCD spectra, are given in Table 2. The Fe(II)/Fe(III) ratio at the surface decreased after reaction with different concentrations of  $H_2O_2$  for all values of x, indicating that magnetically ordered surface Fe(II) was oxidized by H<sub>2</sub>O<sub>2</sub>. This can be seen in Fig. 3B by a decrease in the peak corresponding to Fe(II) in the octahedral sublattice. Fig. 2B shows the change in XMCDderived Fe(II)/Fe(III) ratio at the surface of the nanoparticles, as a function of x, with different concentrations of  $H_2O_2$ . The trend in XMCD-derived Fe(II)/Fe(III) ratios is similar to that for the XRD-derived Fe(II)/Fe(III) ratios (Fig. 2A), with extent of oxidation increasing as a function of x. As with the XRD-derived Fe(II)/Fe(III) ratios, there is little difference between the two most oxidized samples, therefore the extent of oxidation at the

nanoparticle surface is also limited by the characteristics of the particles and not by the concentration of H<sub>2</sub>O<sub>2</sub> in solution.

The major difference between oxidation within the nanoparticle structure (XRD, Fig. 2A) and oxidation at the nanoparticle surface (XMCD, Fig. 2B) is that the Fe(II)/Fe(III) ratios at the surface are higher for all values of x. This is additional evidence that oxidation involves the solid-state migration of Fe(II) from the interior to the particle surface, as described in Pearce *et al.* (2012). The loss of the larger Fe(II) cation from the structure decreases the size of the unit cell of Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles, as measured by XRD, and localization of the Fe(II) to the surface is reflected by the higher XMCD Fe(II)/Fe(III) ratio.

The fact that the surface remains enriched in  $Fe(\pi)$  relative to the interior after oxidation is interesting and counterintuitive. Surface enrichment of Fe(II), even after reaction of  $Fe_{3-x}Ti_xO_4$  nanoparticles with an electron acceptor, i.e., the redox active aqueous contaminant pertechnetate, TcO<sub>4</sub>-, was also observed by Liu et al. (2012). 10 We hypothesize that Ti(IV) may be enriched at the surface of the nanoparticles because of the fast precipitation kinetics during synthesis. Charge balance requires that the surface will also be enriched in Fe(II), despite there being sufficient oxidant in solutions to completely oxidize the nanoparticles. This goes some way to explaining the consistently higher XMCD-derived surface Fe(II)/Fe(III) ratio (vs. XRD-derived bulk Fe(II)/Fe(III) ratio) under different conditions. However, as will be shown below, the surfaces of unsubstituted Fe<sub>3</sub>O<sub>4</sub> nanoparticles are also enriched in Fe(II) relative to the interior upon synthesis.

To test the hypothesis that the titanomagnetite nanoparticle surfaces are enriched in both Ti(IV) and Fe(II), STEM, in combination with EELS mapping, was used to examine the spatial distribution of Ti(IV), Fe(II) and Fe(III) within individual nanoparticles (Fig. 4). STEM-EELS mapping of the x = 0.15 sample after synthesis showed that a core–shell compositional structure is present, in which the shell tends to be relatively

Nanoscale Paper

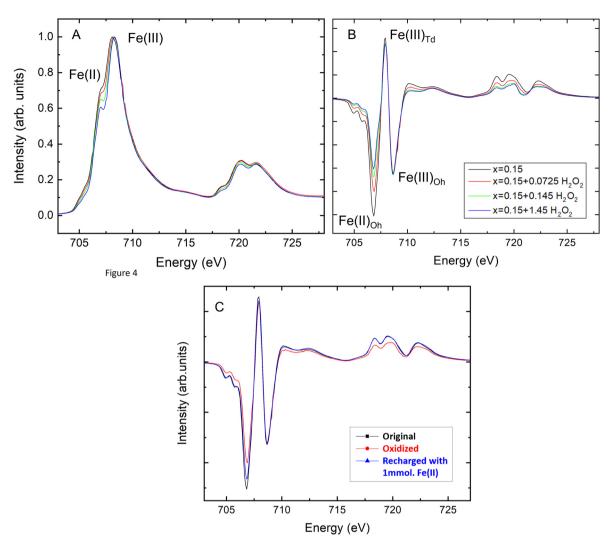


Fig. 3 XA (A) and XMCD (B) spectra for x = 0.15 nanoparticles before and after reaction with different concentrations of H<sub>2</sub>O<sub>2</sub>. (C) XMCD spectra for the x = 0.15 sample before oxidation, after oxidation with 0.0725 H<sub>2</sub>O<sub>2</sub> and after resupply with 1 mmol FeCl<sub>2</sub>.

enriched in Ti relative to the core. The shell can be described as  $\sim 1$  to 4 nm thick, consisting of higher  $\mathrm{Ti}(\mathrm{rv})$  concentrations and corresponding enrichment in Fe(II). Fig. 4B shows that oxygen K-edge peaks in the EELS collected at the edge of the particle (red spectrum) are shifted to higher energy. The inset in Fig. 4B shows that the peak in the EELS corresponding to the Fe L-edge shifts to lower energy, indicating that the iron is more reduced in the shells of the nanoparticles.

Bowles *et al.* (2019)<sup>46</sup> reported a clustered distribution of Ti in titanomagnetite nanoparticles, similarly synthesized, and studied by Mössbauer and XMCD. To investigate the local environment of Ti atoms, Ti and Fe K-edge XANES (Fig. S2†) and EXAFS data were collected for the as-synthesized x = 0.00 and x = 0.15 nanoparticles, and compared to calculated EXAFS (Fig. S3 and Table S1†). Two titanomagnetite models were considered: (i) a magnetite cell with one Ti atom substituting for octahedral Fe(III); and (ii) a magnetite cell with two Ti atoms at octahedral Fe(III) sites. The first model predicts only Ti–Fe paths in the second shell, and the second model has a Ti–Ti

path in addition to Ti–Fe paths in the second shell. The first shell is composed of 6 O atoms in both models. The Ti K-edge EXAFS data (x = 0.15 sample) were noisy, and fitting did not yield reliable parameters to compare with the model that included the Ti–Ti path (fit parameters to the magnetite structure are summarized in Table S1†).

The Fe K-edge data were of better quality, but it was not possible to discern the presence of Fe–Ti paths from the fit to the EXAFS. The reason for this is revealed by a comparison between the calculated Fe K-edge EXAFS for magnetite, with the Fe–Fe path averaged for the tetrahedral and octahedral sites, and the calculated Ti K-edge EXAFS for titanomagnetite, with Ti in two octahedral Fe sites. The  $\chi(k)$  functions are very similar, irrespective of whether the absorber is Fe of Ti (Fig. S4†), making it difficult to discern the presence of Fe–Ti paths in the magnetite structure.

Fe K-edge EXAFS data were then compared with FEFF simulated Fe K-edge EXAFS for a magnetite cell with one or two substituting octahedral Ti atoms. Each of the two simulated

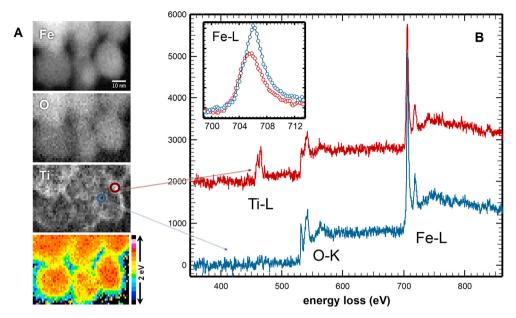


Fig. 4 STEM-EELS of as-synthesized titanomagnetite nanoparticles (x = 0.15): (A) STEM images of nanoparticles (scale bar is 10 nm); (B) EELS spectra collected in the core (blue) and on the edge (red) of a nanoparticle with inset of the enlarged Fe L-region.

spectra was an average of 20 simulations from different Fe atoms (12 in tetrahedral sites and 8 in octahedral sites) within 3.5 Å of a Ti atom. The spectrum simulated for the magnetite structure with two Ti atoms in octahedral Fe<sup>3+</sup> sites more closely resembles the data, as seen from the EXAFS plot and more evident from the Fourier transform imaginary part plot, suggesting clustered Ti distribution in the titanomagnetite nanoparticles (Fig. 5). This is a preliminary result, however, as the ensemble of neighboring Fe atoms was chosen randomly and does not fully represent the Fe local environment of the titanomagnetite cell.

The combination of STEM-EELS results with Ti and Fe K-edge XANES and EXAFS data, shows that the Ti-containing nanoparticles have a core–shell-like structure consisting of a hyperstoichiometric magnetite core, with Ti(rv) and charge balancing Fe(ri) enriched at the surface, and that isolation of the Ti to the surface results in a clustered distribution of Ti atoms in the shell of the  $Fe_{3-x}Ti_xO_4$  (x > 0.00) nanoparticles. The unit cell parameter of titanomagnetite is larger than that of stoichiometric magnetite, and this may induce strain gradients in the confined Ti(rv)/Fe(ri)-enriched shell. Strain in Fe/Feoxide core–shell nanoparticles has been shown to enhance ionic transport and increase the rate of diffusion-limited oxidation reactions, the foreign through the redox reactivity of these  $Fe_{3-x}Ti_xO_4$  (x > 0.00) nanoparticles.

## 3.3 Recharge of oxidized titanomagnetite nanoparticles with $Fe^{2+}$

To investigate the potential for recharge after oxidation, the oxidized  $Fe_{3-x}Ti_xO_4$  ( $x=0.00,\ 0.15$  and 0.38) nanoparticle suspensions were exposed to  $FeCl_2$  solution (4 mmol of  $Fe^{2+}$  per gram of nanoparticles). Fig. S5† shows the uptake of  $Fe^{2+}$  from

the solution by x = 0.00, 0.15 and 0.38 nanoparticles with two different extents of oxidation. Fe<sup>2+</sup> uptake from the solution was almost instantaneous, with 50–80% of uptake occurring within the first 15 min of exposure to the Fe<sup>2+</sup> solution (Fig. S5†).

For a particular value of x, the extent of  $Fe(\pi)$  uptake from solution was related to the XMCD-derived surface Fe(II)/Fe(III) ratio. For example, the x = 0.15 nanoparticles after oxidation with 0.145 mL of H<sub>2</sub>O<sub>2</sub>, with a starting surface Fe(II)/Fe(III) ratio of 0.425, could uptake 3.47 mmol g<sup>-1</sup> Fe<sup>2+</sup> from solution (as determined by ferrozine assay), whereas the x = 0.15 nanoparticles after oxidation with 0.0725 mL of H<sub>2</sub>O<sub>2</sub>, with a starting surface Fe(II)/Fe(III) ratio of 0.552 could only uptake 2.54 mmol g<sup>-1</sup>. However, the extent of Fe<sup>2+</sup> uptake from solution by oxidized Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles with different values of x was not well correlated with the XMCD-derived surface structural Fe(II)/Fe(III), as suggested by the poor linear fit to the data in Fig. 6A ( $R^2 = 0.44$ ). Over the range of three x values, the extent of Fe2+ uptake from the solution was instead better correlated with the XRD-derived whole particle structural Fe(II)/ Fe(III) ratio of the oxidized material (Fig. S5†), as supported by a linear fit with an  $R^2$  value of 0.95 (Fig. 6B).

The linear fit to the overall trend for  $Fe^{2^+}$  uptake  $\nu s$ . the amount of Fe(II) in the solid (derived from the XRD Fe(II)/Fe(III) ratio) was not as good ( $R^2 = 0.71$ ), as shown in Fig. 6C. Thus, it is the Fe(II)/Fe(III) ratio in the whole particle that controls the amount of  $Fe^{2^+}$  uptake, and not the actual Fe(II) amount in the bulk solid. This is supported by Gorski and Scherer (2009)<sup>19</sup> who showed that  $Fe^{2^+}$  uptake depends on magnetite stoichiometry, not initial Fe(II) content, as Fe(II) is not stable and transfers electrons to Fe(III). A thermodynamic model for the magnetite-maghemite solid solution was developed by

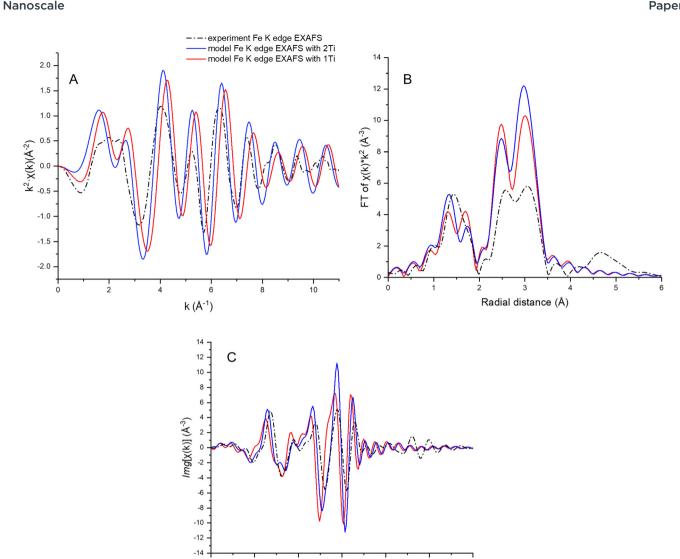


Fig. 5 Fe K-edge (A) EXAFS data, (B) Fourier transform magnitude, and (C) imaginary part for as-synthesized titanomagnetite (x = 0.15) nanoparticles (dotted black line); calculated Fe K-edge EXAFS for magnetite cell with one substituting octahedral Ti atom (red) and with two substituting octahedral Ti atoms (blue).

Radial distance (Å)

Jungcharoen et al. (2022)44 to predict the behavior and transformation of magnetite nanoparticles in aqueous solutions, and the results in Fig. 6C suggest that this model could be extended to tianomagnetite-titanomagnemite solid solution. However, modelling the behavior of the Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles studied here has some additional complications in that the crystallite size increases after Fe(II) recharge (Table 2), and the Ti is not evenly distributed throughout the nanoparticles (Fig. 4). Therefore, Fe<sup>2+</sup> uptake does not correlate as well with the XMCD derived surficial Fe(II)/Fe(III), as was shown in Jungcharoen et al. (2022),44 but instead correlates with the XRD-derived whole particle Fe(II)/Fe(III). Given the trend in Fig. 6C, the stoichiometry of the Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles exposed to pH 8 conditions, partially oxidized by H2O2 and subsequently recharged by Fe<sup>2+</sup>, could potentially be predicted

by an equilibrium model, if the XRD-derived Fe(II)/Fe(III) is used.

The amount of structural Fe(II) recharge in the Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles (x = 0.00, x = 0.15 and x = 0.38) was calculated by using the Fe(II) concentrations derived from the XRD Fe(II)/Fe (III) ratio and subtracting the amount of Fe(II) in the oxidized nanoparticles from the amount of Fe(II) in the recharged nanoparticles. Fig. 6D shows that the amount of Fe<sup>2+</sup> uptake from solution can be related to the amount of Fe(II) recharge in the solid by a linear fit with an  $R^2$  value of 0.90. However, the amount of Fe<sup>2+</sup> uptake from the solution is approximately twice the amount of Fe(II) recharge in the solid. The crystallite size, as determined by XRD, increased by 1-2 nm after Fe(II) recharge, suggesting that the extra Fe2+ uptake from the solution could be explained by growth of the nanoparticles

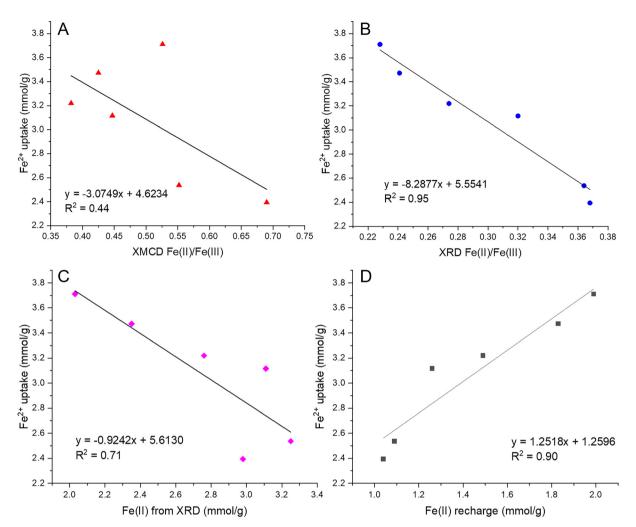


Fig. 6 Linear regression plots for  $Fe^{2+}$  uptake (mmol  $g^{-1}$ ) from the solution (as determined by ferrozine assay) for  $Fe_{3-x}Ti_xO_4$  nanoparticles (x=0.00, 0.15 and 0.38), plotted as one dataset in each figure, vs. (A) XMCD-derived surface Fe(ii)/Fe(iii) ratios after oxidation, (B) XRD-derived whole particle Fe(ii)/Fe(iii) ratios after oxidation, and (C) XRD-derived whole particle Fe(ii) (mmol  $g^{-1}$ ) after oxidation; (D) Fe(ii) recharge (mmol  $g^{-1}$ ) estimated from the XRD-derived Fe(ii) in the recharged nanoparticles minus the Fe(ii) in the oxidized nanoparticles.


(Table 2). The Ti/Fe ratio at the surface of the  $Fe_{3-x}Ti_xO_4$  nanoparticles (x > 1) was calculated from the integrated area of the XA spectra for the Fe and Ti  $L_{2,3}$ -edges taken at the same point on the sample, after background subtraction as described in Droubay (1999). In general, there was a small decrease in Ti/Fe ratio after  $Fe(\pi)$  recharge, indicating that the surface was slightly enriched in Fe. However, the Ti/Fe ratio did not change significantly, suggesting that the composition of the surface was not drastically altered by  $Fe(\pi)$  recharge. This was also confirmed by TEM of a representative particle from the x=0.15 sample after  $Fe(\pi)$  recharge (Fig. 1C). The particle in Fig. 1C has a similar morphology to those in Fig. 1A and B, with continuous lattice fringes to the edge of the particle, suggesting that it is structurally homogeneous with no evidence of a different surface phase.

To obtain further information on the Fe( $\pi$ )/Fe( $\pi$ ) ratio and the Fe site occupancy at the surface of the recharged Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticle suspensions, the samples were ana-

lyzed by XMCD. Fig. 3C shows the XMCD spectra for the x = 0.15 sample before oxidation, after oxidation with  $H_2O_2$  and after resupply with  $FeCl_2$ , normalized to the intensity of the octahedral Fe(III) peak. A significant amount of Fe(II) was lost from the B-site during oxidation and Fig. 3C shows that this site was refilled because of  $Fe^{2+}$  resupply. Despite the presence of a higher  $Fe^{2+}$  concentration in the solution than would be required to refill the B-site, it is not restored to its original site occupancy in any of the samples.

Fig. 7 shows the different steps in the treatment of the  $Fe_{3-x}Ti_xO_4$  nanoparticle suspensions, characterized by their Fe(II)/Fe(III) ratio in the whole particle from XRD and at the surface from XMCD, for the as-synthesized nanoparticles (step 1), nanoparticles oxidized with lower concentrations of  $H_2O_2$  (step 2), nanoparticles oxidized with higher concentrations of  $H_2O_2$  (step 3), oxidized nanoparticles recharged with lower concentrations of  $Fe^{2+}$  (step 4), and oxidized nanoparticles recharged with higher concentrations of  $Fe^{2+}$  (step 5). For all

Nanoscale

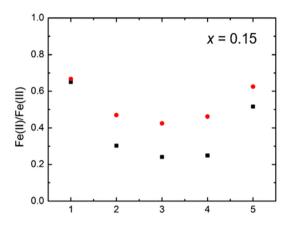

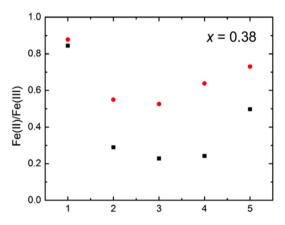


Fig. 7 XMCD (red) and XRD (black) Fe(ii)/Fe(iii) ratios for different steps of Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticle suspensions treatment, starting from synthesized material (step 1) and proceeding through oxidation with lower concentrations of H<sub>2</sub>O<sub>2</sub> (step 2), oxidation with higher concentrations of H<sub>2</sub>O<sub>2</sub> (step 3), recharge with 0.05 mmol Fe<sup>2+</sup> (step 4) to recharge with 2.5 mmol Fe<sup>2+</sup> (step 5).

nanoparticle samples, oxidation decreased the XRD-derived whole particle Fe(II)/Fe(III) ratio to a greater extent than the XMCD-derived surface Fe(II)/Fe(III) ratio, producing a discrepancy between the two. For as-synthesized x=0.00 nano-

particles, the Fe(II)/Fe(III) ratio should be close to that for stoichiometric Fe<sub>3</sub>O<sub>4</sub> (0.5). However, Fig. 7 (x = 0.00) shows that assynthesized x = 0.00 nanoparticles (step 1) had excess Fe(II) in the whole particle (XRD Fe(II)/Fe(III) = 0.556) and at the surface (XMCD Fe(II)/Fe(III) = 0.604), possibly due to rapid precipitation kinetics during synthesis. After oxidation then resupply with high concentrations of Fe<sup>2+</sup> (step 5), both the XRD and XMCD derived Fe(II)/Fe(III) became close to 0.5 (step 5). For as-synthesized Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles (x = 0.15 and x = 0.38), both XRD Fe(II)/Fe(III) and XMCD Fe(II)/Fe(III) increased with x, as replacement of Fe(III) by Ti(IV) in the magnetite structure is accompanied by reduction of structural Fe(III) to Fe(III) for change balance, yielding a proportional increase in Fe(III)/Fe(III).

For the x = 0.15 and x = 0.38 nanoparticles, the surface remained enriched with Fe(II) after the oxidation-recharge cycle (XMCD Fe(II)/Fe(III) of  $\sim$ 0.6 and  $\sim$ 0.7, respectively, in step 5). However, the whole particle Fe(II) was never refilled to the same extent as at the surface (XRD Fe(II)/Fe(III) of 0.5 for both x= 0.15 and x = 0.38 in step 5), and the discrepancy increases with x. Redistribution of cations in the lattice during magnetite oxidation is known, 49 and similar observations were reported for synthesized 10 nm magnetite nanoparticles which were recrystallized into stoichiometric magnetite after an oxidation-recharge cycle.18 Results presented in Fig. 7 show that, while Fe(II) enrichment at the surface is preserved for the titanomagnetite nanoparticles after the oxidation and recharge cycle, the final whole particle XRD-derived Fe(II)/Fe(III) ratio approaches that for stoichiometric magnetite (0.5) for both magnetite and titanomagnetite nanoparticles.

# 3.4 Reaction of oxidized and recharged titanomagnetite nanoparticles with ${\rm TcO_4}^-$

Reduction experiments were conducted using Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles (x = 0.15) to evaluate the effect of the oxidationrecharge cycle on reduction of Tc(vII)O4-. Dependence of  $TcO_4$  reduction on the amount of Ti (x = 0.00, 0.15, 0.25, 0.38, and 0.53) in as-synthesized Fe<sub>3-x</sub>Ti<sub>x</sub>O<sub>4</sub> nanoparticles was investigated previously at initial TcO<sub>4</sub><sup>-</sup> concentrations of 10 and 30 μM, <sup>10</sup> which showed higher TcO<sub>4</sub> reduction rates with larger x. After 4 hours, x = 0.00 nanoparticles only reduced 30% of the TcO<sub>4</sub><sup>-</sup>, in solutions with the same starting concentration as used here (10 μM). Reduction of TcO<sub>4</sub> by as-synthe sized x = 0.15 nanoparticles increased to ~70%, showing that doping magnetite nanoparticles with Ti(IV) increases their redox reactivity. However, a study of the reduction of U(v1), as uranyl acetate, by x = 0.5 nanoparticles with different extents of oxidation, revealed the controlling effect of Fe(II)/Fe(III) ratio over variable Ti(IV) content. 12 A higher Fe(II)/Fe(III) ratio enhances the accessibility of reducing equivalents localized on octahedral Fe(II)-Fe(III) pairs. 19,50 Here, TcO<sub>4</sub> removal from the solution was the highest with the as-synthesized hyperstoichiometric x = 0.15 nanoparticles (Fig. 7B, step 1), but was negligible with oxidized nanoparticles, and was partially restored after recharge, depending on the amount of Fe2+ that was resupplied (0.5 mmol vs. 1 mmol of FeCl<sub>2</sub>) (Fig. 8). The highest redox reactivity can be attributed to the excess of Fe(II), in the

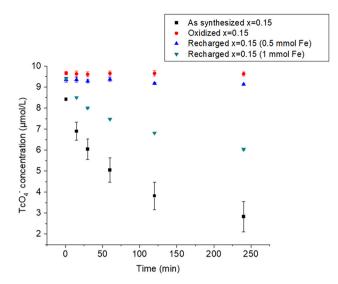


Fig. 8  $TcO_4^-$  reduction kinetics in x=0.15 nanoparticles: as-synthesized material, oxidized material, and oxidized material recharged with 0.5 and 1 mmol FeCl<sub>2</sub>.

whole particle and at the surface, that was present in the x =0.15 nanoparticles because of rapid precipitation during synthesis. The partially restored redox reactivity of the x = 0.15nanoparticles after recharge can be explained by the lower, near stoichiometric structural Fe(II)/Fe(III) ratio of 0.5 (Fig. 7, step 5). Hence, while the redox reactivity of x = 0.15 nanoparticles is affected by the additional Fe(II) required to charge balance Ti(IV) substitution, it is mainly controlled by the electron transfer through structural Fe(II)-Fe(III) pairs, enhanced by the excess Fe(II) in the rapidly precipitated hyperstoichiometric x = 0.15 starting material. Even though surface Fe(II)/Fe(III)ratio was restored during recharge, the whole particle Fe(II)/Fe (III) ratio was not restored (Fig. 7). The lower reduction capacity of the x = 0.15 nanoparticles after recharge, compared to that for starting material, demonstrates that reduction of TcO<sub>4</sub>requires the resupply of Fe(II) from the nanoparticle interior, to replenish the oxidized Fe(II) at the surface. The whole particle  $Fe(\pi)/Fe(\pi)$  ratio is only recharged to 0.5, *i.e.*, that for x = 0.00, resulting in a smaller pool of reactive Fe(II), and a reduction capacity that is closer to the x = 0.00 nanoparticles in Liu et al.  $(2012)^{10}$  than to the x = 0.15 starting material (Fig. 8).

In addition, the  $Fe_{3-x}Ti_xO_4$  (x > 0.00) nanoparticles have a core–shell-like structure consisting of a hyperstoichiometric magnetite core, with Ti(IV) and charge balancing Fe(II) enriched at the surface, and may exhibit strain-enhanced ionic conduction, resulting in increased reactivity. During oxidation and recharge, diffusion of Fe(II) cations and vacancies can give rise to structural reorganization and a lower degree of structural disorder, as shown by a smaller spin canting of partially oxidized magnetite compared to the pristine stoichiometric magnetite. This structural reorganization could relieve some of the strain in the  $Fe_{3-x}Ti_xO_4$  (x > 0.00) nanoparticles and explain why the reduction capacity of the x = 0.15 nanoparticles after recharge is lower compared to that for starting material.

### 4. Conclusions

The series of synthetic  $Fe_{3-x}Ti_xO_4$  nanoparticles with different amounts of substituted Ti(v) (x = 0.00, 0.15, 0.38) were investigated to determine the potential for Fe(II) recharge and restoration of reduction capacity after oxidation with H<sub>2</sub>O<sub>2</sub>. We found that rapid precipitation during Fe3-xTixO4 nanoparticle synthesis led to enrichment of substituted Ti(IV) at the surface. The Fe(II)/Fe(III) ratio was determined to be: (i) dependent on x(amount of Ti(IV) requiring Fe(II) for charge balance); (ii) higher at the surface of nanoparticles, determined by surface sensitive XMCD analysis vs. whole particle XRD analysis; (iii) higher at the surface of titanomagnetite nanoparticles after oxidation, compared to magnetite nanoparticles after oxidation; (iv) representative of nearly stoichiometric magnetite for the whole titanomagnetite nanoparticle while remaining higher at the surface after nanoparticle recharge. Ti(w) substitution increased the amount of Fe(II) available for TcO4reduction, and the reduction capacity was controlled by electron transfer from Fe(II)-Fe(III) pairs in the interior to the surface of the  $Fe_{3-x}Ti_xO_4$  nanoparticles.

This study shows that titanium substitution increases the solid-state Fe(II)/Fe(III) ratio in titanomagnetite, making them promising low-cost, high-efficiency reductants with 'tunable' reactivity for environmental remediation applications. In addition, natural titanomagnetites exhibit a range of Ti contents, and their structural Fe(II)/Fe(III) ratio can be modified by changing redox conditions resulting from fluctuating water levels. The results presented here show that these materials also display reversibility with respect to reincorporation of Fe (II) into the structure upon exposure to reducing microenvironments creating, for example, by microbial activity. This new understanding of the effects of changing titanomagnetite stoichiometry on redox reactivity is of relevance to remediation of redox active contaminants, e.g., technetium, uranium, and chromium, present in the subsurface at legacy nuclear sites associated with past nuclear weapons production, testing, and energy research.

### Conflicts of interest

There are no conflicts of interest to declare.

### Data availability

The data supporting this article have been included as part of the ESI.†

### Acknowledgements

This material is based upon work supported by the U.S. Department of Energy (DOE) Office of Science, Office of Basic Energy Sciences, Chemical Sciences, Geosciences, and Biosciences Division through its Geosciences program at

Pacific Northwest National Laboratory (PNNL) (FWP 56674). The authors gratefully acknowledge Bernd Kabius and Robert Colby for TEM/EELS mapping data. A portion of the work was carried out in the Environmental and Molecular Sciences Laboratory (EMSL), a national scientific user facility at PNNL sponsored by the DOE Office of Biological and Environmental Research. XA and XMCD measurements were performed at the Advance Light Source supported by the DOE Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-05CH11231. Use of the Advanced Photon Source, an Office of Science User Facility operated for the U.S. Department of Energy (DOE) Office of Science by Argonne National Laboratory, was supported by the U.S. DOE under Contract No. DE-AC02-06CH11357. PNNL is a multiprogram national laboratory operated by Battelle Memorial Institute under contract no.

### References

DE-AC05-76RL01830 for the DOE.

Nanoscale

- 1 A. Thompson, O. A. Chadwick, D. G. Rancourt and J. Chorover, Iron-oxide crystallinity increases during soil redox oscillations, *Geochim. Cosmochim. Acta*, 2006, **70**(7), 1710–1727.
- 2 J. J. Papike, J. M. Karner and C. K. Shearer, Comparative planetary mineralogy: Valence state partitioning of Cr, Fe, Ti, and V among crystallographic sites in olivine, pyroxene, and spinel from planetary basalts, *Am. Mineral.*, 2005, **90**(2–3), 277–290.
- 3 Z. Wang, J. Ma, J. Li, T. Zeng, Z. Zhang, X. He, L. Zhang and G. Wei, Effect of Fe–Ti oxides on Mo isotopic variations in lateritic weathering profiles of basalt, *Geochim. Cosmochim. Acta*, 2020, **286**, 380–403.
- 4 O. Orlický, F. Caňo, J. Lipka, A. Mihaliková and B. Toman, Fe-Ti magnetic minerals of basaltic rocks: a study of their nature and composition, *Geol. Carpathica*, 1992, 43(5), 287–293.
- 5 W. O'reilly and S. K. Banerjee, Cation distribution in titanomagnetites (1-x)Fe<sub>3</sub>O<sub>4</sub> xFe<sub>2</sub>TiO<sub>4</sub>, *Physics Letters*, 1965, 17(3), 237–238.
- 6 S. K. Banerjee, W. O'reilly, T. C. Gibb and N. N. Greenwood, The behaviour of ferrous ions in iron-titanium spinels, *J. Phys. Chem. Solids*, 1967, **28**(7), 1323–1335.
- 7 C. I. Pearce, C. M. Henderson, N. D. Telling, R. A. Pattrick, J. M. Charnock, V. S. Coker, E. Arenholz, F. Tuna and G. van der Laan, Fe site occupancy in magnetite-ulvospinel solid solutions: A new approach using X-ray magnetic circular dichroism, *Am. Mineral.*, 2010, 95(4), 425–439.
- 8 C. I. Pearce, O. Qafoku, J. Liu, E. Arenholz, S. M. Heald, R. K. Kukkadapu, C. A. Gorski, C. M. Henderson and K. M. Rosso, Synthesis and properties of titanomagnetite (Fe3- xTixO4) nanoparticles: A tunable solid-state Fe(II/III) redox system, *J. Colloid Interface Sci.*, 2012, 387(1), 24-38.
- 9 H. U. Worm and S. K. Banerjee, Aqueous low-temperature oxidation of titanomagnetite, *Geophys. Res. Lett.*, 1984, 11(3), 169–172.

- 10 J. Liu, C. I. Pearce, O. Qafoku, E. Arenholz, S. M. Heald and K. M. Rosso, Tc(vII) reduction kinetics by titanomagnetite (Fe3- xTixO4) nanoparticles, *Geochim. Cosmochim. Acta*, 2012, 92, 67-81.
- 11 R. Marsac, M. Pasturel and K. Hanna, Reduction kinetics of nitroaromatic compounds by titanium-substituted magnetite, *J. Phys. Chem. C*, 2017, **121**(21), 11399–11406.
- 12 D. E. Latta, C. I. Pearce, K. M. Rosso, K. M. Kemner and M. I. Boyanov, Reaction of UVI with titanium-substituted magnetite: Influence of Ti on UIV speciation, *Environ. Sci. Technol.*, 2013, 47(9), 4121–4130.
- 13 E. M. Wylie, D. T. Olive and B. A. Powell, Effects of titanium doping in titanomagnetite on neptunium sorption and speciation, *Environ. Sci. Technol.*, 2016, **50**(4), 1853–1858.
- 14 R. Ding, C. Guida, C. I. Pearce, E. Arenholz, J. M. Grenèche, A. Gloter, A. C. Scheinost, K. O. Kvashnina, K. Wang, A. Fernandez-Martinez, Y. Mu, K. M. Rosso and L. Charlet, Single rhenium atoms on nanomagnetite: Probing the recharge process that controls the fate of rhenium in the environment, *Sci. Adv.*, 2025, 11(20), eadq3650.
- 15 M. L. Peterson, A. F. White, G. E. Brown and G. A. Parks, Surface passivation of magnetite by reaction with aqueous Cr(v1): XAFS and TEM results, *Environ. Sci. Technol.*, 1997, 31(5), 1573–1576.
- 16 J. Scaria, M. Pédrot, L. Fablet, T. Yomogida, T. T. Nguyen, Y. Sivry, C. Catrouillet, A. E. Pradas Del Real, F. Choueikani, D. Vantelon, A. Dia, A. Groleau and R. Marsac, Magnetite Stoichiometry (Fe(II)/Fe(III)) Controls on Trivalent Chromium Surface Speciation, *Environ. Sci. Technol.*, 2025, 59(11), 5747-5755.
- 17 M. L. Peterson, G. E. Brown Jr and G. A. Parks, Direct XAFS evidence for heterogeneous redox reaction at the aqueous chromium/magnetite interface, *Colloids Surf.*, *A*, 1996, **107**, 77–88.
- 18 P. Jungcharoen, M. Pédrot, F. Choueikani, M. Pasturel, K. Hanna, F. Heberling, M. Tesfa and R. Marsac, Probing the effects of redox conditions and dissolved Fe 2 + on nanomagnetite stoichiometry by wet chemistry, XRD, XAS and XMCD, *Environ. Sci.: Nano*, 2021, 8(7), 2098–2107.
- 19 C. A. Gorski and M. M. Scherer, Influence of magnetite stoichiometry on FeII uptake and nitrobenzene reduction, *Environ. Sci. Technol.*, 2009, 43(10), 3675–3680.
- 20 J. M. Byrne, N. Klueglein, C. Pearce, K. M. Rosso, E. Appel and A. Kappler, Redox cycling of Fe(II) and Fe(III) in magnetite by Fe-metabolizing bacteria, *Science*, 2015, 347(6229), 1473–1476.
- 21 J. M. Byrne, G. Van Der Laan, A. I. Figueroa, O. Qafoku, C. Wang, C. I. Pearce, M. Jackson, J. Feinberg, K. M. Rosso and A. Kappler, Size dependent microbial oxidation and reduction of magnetite nano-and micro-particles, *Sci. Rep.*, 2016, 6(1), 30969.
- 22 K. Schwochau, *Technetium: chemistry and radiopharmaceuti*cal applications, John Wiley & Sons, 2008 Nv 21.
- 23 L. L. Stookey, Ferrozine—a new spectrophotometric reagent for iron, *Anal. Chem.*, 1970, **42**(7), 779–781.

- 24 E. Arenholz and S. O. Prestemon, Design and performance of an eight-pole resistive magnet for soft X-ray magnetic dichroism measurements, Rev. Sci. Instrum., 2005, 76(8), 083908.
- 25 S. Gota, M. Gautier-Soyer and M. Sacchi, Fe 2 p absorption in magnetic oxides: Quantifying angular-dependent saturation effects, Phys. Rev. B: Condens. Matter Mater. Phys., 2000, 62(7), 4187.
- 26 R. A. Pattrick, G. Van Der Laan, C. M. Henderson, P. Kuiper, E. Dudzik and D. J. Vaughan, Cation site occupancy in spinel ferrites studied by X-ray magnetic circular dichroism: developing a method for mineralogists, Eur. J. Mineral., 2002, 14(6), 1095-1102.
- 27 G. Van der Laan and I. W. Kirkman, The 2p absorption spectra of 3d transition metal compounds in tetrahedral and octahedral symmetry, J. Phys.: Condens. Matter, 1992, 4(16), 4189.
- 28 G. Van der Laan and B. T. Thole, Strong magnetic X-ray dichroism in 2p absorption spectra of 3d transition-metal ions, Phys. Rev. B: Condens. Matter Mater. Phys., 1991, 43(16), 13401.
- 29 V. S. Coker, N. D. Telling, G. Van Der Laan, R. A. Pattrick, C. I. Pearce, E. Arenholz, F. Tuna, R. E. Winpenny and J. R. Lloyd, Harnessing the extracellular bacterial production of nanoscale cobalt ferrite with exploitable magnetic properties, ACS Nano, 2009, 3(7), 1922-1928.
- 30 B. Ravel and M. A. Newville, ATHENA, ARTEMIS, HEPHAESTUS: data analysis for X-ray absorption spectroscopy using IFEFFIT, Synchrotron Radiat., 2005, 12(4), 537-541.
- 31 C. Haavik, S. Stølen, H. Fjellvag, M. Hanfland and D. Hausermann, Equation of state of magnetite and its high-pressure modification: Thermodynamics of the Fe-O system at high pressure, Am. Mineral., 2000, 85(3-4), 514-523.
- 32 J. P. Perdew, K. Burke and M. Ernzerhof, Generalized gradient approximation made simple, Phys. Rev. Lett., 1996, 77(18), 3865.
- 33 S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys and A. P. Sutton, Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+ U study, Phys. Rev. B: Condens. Matter Mater. Phys., 1998, 57(3), 1505.
- 34 G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, Phys. Rev. B: Condens. Matter Mater. Phys., 1996, 54(16), 11169.
- 35 P. E. Blöchl, Projector augmented-wave method, Phys. Rev. B: Condens. Matter Mater. Phys., 1994, 50(24), 17953.
- 36 J. J. Kas, F. D. Vila, C. D. Pemmaraju, T. S. Tan and J. J. Rehr, Advanced calculations of X-ray spectroscopies with FEFF10 and Corvus, Synchrotron Radiat., 2021, 28(6),
- 37 B. A. Wechsler, D. H. Lindsley and C. T. Prewitt, Crystal structure and cation distribution in titanomagnetites  $(Fe_{3-x}Ti_xO_4)$ , Am. Mineral., 1984, **69**(7-8), 754-770.

- 38 F. Bosi, U. Hålenius and H. Skogby, Crystal chemistry of the magnetite-ulvospinel series, Am. Mineral., 2009, 94(1), 181-189.
- 39 G. Van der Laan, J. Zaanen, G. A. Sawatzky, R. Karnatak and J. M. Esteva, Comparison of X-ray absorption with X-ray photoemission of nickel dihalides and NiO, Phys. Rev. B: Condens. Matter Mater. Phys., 1986, 33(6), 4253.
- 40 C. T. Chen, Y. U. Idzerda, H. J. Lin, N. V. Smith, G. Meigs, E. Chaban, G. H. Ho, E. Pellegrin and F. Sette, Experimental confirmation of the X-ray magnetic circular dichroism sum rules for iron and cobalt, Phys. Rev. Lett., 1995, 75(1), 152.
- 41 J. Stöhr, X-ray magnetic circular dichroism spectroscopy of transition metal thin films, J. Electron Spectrosc. Relat. Phenom., 1995, 75, 253-272.
- 42 M. Sassi, C. I. Pearce, P. S. Bagus, E. Arenholz and K. M. Rosso, First-principles Fe L2, 3-edge and O K-edge XANES and XMCD spectra for iron oxides, J. Phys. Chem. A, 2017, 121(40), 7613-7618.
- 43 E. Demangeat, M. Pédrot, A. Dia, M. Bouhnik-le-Coz, F. Grasset, K. Hanna, M. Kamagate and F. Cabello-Hurtado, Colloidal and chemical stabilities of iron oxide nanoparticles in aqueous solutions: the interplay of structural, chemical and environmental drivers, Environ. Sci.: Nano, 2018, 5(4), 992-1001.
- 44 P. Jungcharoen, M. Pédrot, F. Heberling, K. Hanna, F. Choueikani, C. Catrouillet, A. Dia and R. Marsac, Prediction of nanomagnetite stoichiometry (Fe(II)/Fe(III)) under contrasting pH and redox conditions, Environ. Sci.: Nano, 2022, 9(7), 2363-2371.
- 45 P. A. Van Aken, B. Liebscher and V. J. Styrsa, Quantitative determination of iron oxidation states in minerals using 3-edge electron energy-loss structure spectroscopy, Phys. Chem. Miner., 1998, 25, 323-327.
- 46 J. A. Bowles, S. C. Lappe, M. J. Jackson, E. Arenholz and G. van der Laan, Curie temperature enhancement and cation ordering in titanomagnetites: evidence from magnetic properties, XMCD, and Mössbauer spectroscopy, Geochem., Geophys., Geosyst., 2019, 20(5), 2272-2289.
- 47 A. Pratt, L. Lari, O. Hovorka, A. Shah, C. Woffinden, S. P. Tear, C. Binns and R. Kröger, Enhanced oxidation of nanoparticles through strain-mediated ionic transport, Nat. Mater., 2014, 13(1), 26-30.
- 48 T. C. Droubay, Soft X-ray spectroscopy and microspectroscopy of magnetic and naturally occurring materials, The University of Wisconsin-Milwaukee, 1999.
- 49 R. Bliem, E. McDermott, P. Ferstl, M. Setvin, O. Gamba, J. Pavelec, M. A. Schneider, M. Schmid, U. Diebold, P. Blaha and L. Hammer, Subsurface cation vacancy stabilization of the magnetite (001) surface, Science, 2014, **346**(6214), 1215–1218.
- 50 C. A. Gorski, J. T. Nurmi, P. G. Tratnyek, T. B. Hofstetter and M. M. Scherer, Redox behavior of magnetite: Implications for contaminant reduction, Environ. Sci. Technol., 2010, 44(1), 55-60.