



Cite this: *Nanoscale*, 2025, **17**, 15436

## Direct thermal atomic layer deposition of high- $\kappa$ dielectrics on monolayer MoS<sub>2</sub>: nucleation and growth†

Brendan F. M. Healy,<sup>ID</sup> \* Sophie L. Pain,<sup>ID</sup> Nicholas E. Grant<sup>ID</sup> and John D. Murphy<sup>ID</sup>

High dielectric constant (high- $\kappa$ ) materials must be successfully integrated with single-layer transition metal dichalcogenides for future nanoscale device technologies. With high carrier mobility and relatively strong visible light emission, monolayer molybdenum disulfide (1L MoS<sub>2</sub>) is a promising candidate for optoelectronic applications and is commonly synthesised *via* chemical vapour deposition (CVD) to enable large-area device production. The growth of uniform high- $\kappa$  dielectrics on bulk materials is routinely achieved *via* thermal atomic layer deposition (ALD), but continuous deposition on MoS<sub>2</sub> is notoriously challenging due to the absence of dangling bonds on the basal plane. The resulting unique nucleation and growth characteristics of high- $\kappa$  dielectrics on 1L MoS<sub>2</sub> are not fully understood, particularly on large-area CVD-1L MoS<sub>2</sub>. In this work, we investigate the nucleation and growth of aluminium oxide (Al<sub>2</sub>O<sub>3</sub>) and hafnium dioxide (HfO<sub>2</sub>) on CVD-1L MoS<sub>2</sub> films *via* direct thermal ALD at 200 °C. We vary the number of ALD cycles and monitor the morphology of the deposited high- $\kappa$  layer *via* atomic force microscopy, observing ALD-Al<sub>2</sub>O<sub>3</sub> and ALD-HfO<sub>2</sub> films on CVD-1L MoS<sub>2</sub> to exhibit island features for all cycle numbers investigated (up to 200 cycles). We reveal the development of Al<sub>2</sub>O<sub>3</sub> on CVD-1L MoS<sub>2</sub> proceeds *via* a three-dimensional growth mode, and we estimate the vertical and lateral growth rates to be  $0.09 \pm 0.01$  nm per cycle and  $0.06 \pm 0.01$  nm per cycle, respectively. In contrast, we find direct ALD of HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub> exhibits negligible lateral growth, with a vertical growth rate of  $0.14 \pm 0.01$  nm per cycle. We also investigate the thickness-dependent effects of ALD-Al<sub>2</sub>O<sub>3</sub> and ALD-HfO<sub>2</sub> films on the Raman and photoluminescence character of CVD-1L MoS<sub>2</sub>, and quantify changes in electron density. Our growth study offers valuable insights into the nucleation and development of high- $\kappa$  dielectric films on CVD-1L MoS<sub>2</sub>, enhancing the understanding of dielectric integration for MoS<sub>2</sub>-based devices.

Received 19th March 2025,  
Accepted 8th June 2025

DOI: 10.1039/d5nr01144b

rsc.li/nanoscale

## Introduction

With novel electrical, optical, and mechanical properties at single-layer thickness, transition metal dichalcogenides (TMDCs) are a class of two-dimensional (2D) layered materials that have attracted considerable research attention. Monolayer molybdenum disulfide (1L MoS<sub>2</sub>) is a prototypical semiconducting TMDC, with a direct bandgap of  $\sim 1.8$  eV.<sup>1,2</sup> 1L MoS<sub>2</sub> comprises a hexagonally arranged plane of Mo atoms, stacked

between two planes of S atoms.<sup>3</sup> Covalent bonding yields strong in-plane stability, with comparatively weak inter-layer van der Waals (vdW) forces holding the S–Mo–S planes together in the bulk MoS<sub>2</sub> structure.<sup>4</sup> With a monolayer thickness of  $\sim 0.7$  nm,<sup>2,5,6</sup> the atomically thin geometry, coupled with the direct bandgap and high carrier mobility, renders 1L MoS<sub>2</sub> desirable for inclusion in numerous nanoscale electronic and optoelectronic technologies, including photovoltaic cells,<sup>7–10</sup> photodetectors,<sup>11,12</sup> and field-effect transistors (FETs).<sup>6,13,14</sup>

The deposition of high dielectric constant (high- $\kappa$ ) materials, commonly aluminium oxide (Al<sub>2</sub>O<sub>3</sub>) or hafnium dioxide (HfO<sub>2</sub>), on 1L MoS<sub>2</sub> is often required for realisation of devices based on the FET architecture, providing the gate dielectric that electrostatically controls the channel conductivity.<sup>15</sup> Atomic layer deposition (ALD), a variant of chemical vapour deposition (CVD), is a vapour phase deposition technique commonly utilised for the growth of dielectric films for

School of Engineering, University of Warwick, Coventry, CV4 7AL, UK.

E-mail: [brendan.f.m.healy@warwick.ac.uk](mailto:brendan.f.m.healy@warwick.ac.uk)

† Electronic supplementary information (ESI) available: Characterisation of 1L MoS<sub>2</sub>, further AFM images of ALD-Al<sub>2</sub>O<sub>3</sub> and -HfO<sub>2</sub> films, evaluation of island height in ALD-Al<sub>2</sub>O<sub>3</sub> film after 200 cycles, estimation of ALD-HfO<sub>2</sub> thickness on 1L MoS<sub>2</sub>, PL mapping data, deconvoluted single-spot PL spectra, single-spot and mapping Raman data, and correlative analysis of strain and doping in 1L MoS<sub>2</sub>. See DOI: <https://doi.org/10.1039/d5nr01144b>



nanoscale devices. The ALD process proceeds *via* the sequential introduction of gaseous precursor and co-reactant molecules, with purge steps between each reactant pulse ensuring the resultant film forms from the self-terminating chemical reaction of these two species on the substrate surface.<sup>16,17</sup> ALD can achieve excellent film uniformity and conformality on conventional three-dimensional (3D) materials, offering precise control over the deposited film thickness.<sup>18–20</sup> However, since the surface chemistry of monolayer TMDCs varies considerably from that of bulk 3D materials, the ALD of dielectrics on 1L MoS<sub>2</sub> behaves differently. Unlike common 3D substrates, the basal plane of a 2D TMDC is chemically inert, lacking the out-of-plane dangling bonds that facilitate chemisorption of ALD reactants and yield rapid layer closure.<sup>21,22</sup> The metal precursor and oxidising co-reactant instead adsorb onto the 1L MoS<sub>2</sub> surface *via* relatively weak physisorption, and are easily detached at elevated temperatures or during extensive purge steps.<sup>23</sup> Therefore, the generation of thin, uniform dielectric layers on 1L MoS<sub>2</sub> *via* ALD is challenging. Direct ALD, where no pre-treatment of the surface is performed, of dielectric materials on mechanically exfoliated 1L MoS<sub>2</sub> has been shown to proceed *via* an island growth mode. This results in slow closure of the dielectric layer, yielding discontinuous films even at relatively high thicknesses,<sup>24,25</sup> exemplified in our recent report of incomplete Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> films grown on CVD-1L MoS<sub>2</sub> *via* direct thermal ALD.<sup>26</sup> Numerous studies have explored a range of strategies to improve ALD-nucleation on MoS<sub>2</sub>, namely oxide buffer layers,<sup>27,28</sup> plasma pre-treatment,<sup>24,29</sup> and ultraviolet-ozone (UV-O<sub>3</sub>) exposure.<sup>30–32</sup> However, such treatments prior to deposition may have deleterious impacts on the dielectric/MoS<sub>2</sub> interface, so direct ALD processes are deemed preferable. Direct plasma-enhanced (PEALD) of high- $\kappa$  dielectrics, while beneficial for growth on 3D materials, has been shown to degrade the crystal structure of 1L MoS<sub>2</sub> *via* substantial oxidation.<sup>33</sup> Alternatively, tuning the thermal ALD process conditions may improve the growth of ALD-dielectric films on MoS<sub>2</sub>, with lower deposition temperatures thought to encourage physisorption of the ALD precursors on MoS<sub>2</sub>, thus yielding enhanced dielectric surface coverage.<sup>22,25</sup> Despite improved growth, low-temperature ALD processes often result in poor-quality dielectric layers with compromised device performance.<sup>34</sup> Therefore, an optimised direct thermal ALD process is important for the growth of high-quality high- $\kappa$  dielectric films on 1L MoS<sub>2</sub>.

While the growth characteristics of dielectrics on standard 3D substrates are well established, the unique nucleation and growth processes associated with the direct thermal ALD of dielectrics on 1L MoS<sub>2</sub> are not fully understood.<sup>35</sup> In the literature, the vertical growth per cycle (GPC) associated with the deposition of high- $\kappa$  dielectrics on MoS<sub>2</sub> on a silicon-supported silicon dioxide (SiO<sub>2</sub>/Si) substrate is commonly estimated *via* ellipsometry experiments on companion silicon (Si) or silicon dioxide (SiO<sub>2</sub>) substrates. Many studies often assume that the vertical growth rate for a given dielectric on SiO<sub>2</sub>/Si-supported MoS<sub>2</sub> will be approximately equal to that obtained for a SiO<sub>2</sub>/Si wafer.<sup>22,24,36–39</sup> With the surface reactivity of

TMDCs known to differ substantially from that of bulk 3D materials, this assumption may yield incorrect estimation of the vertical GPC that does not accurately reflect the development of ALD-grown high- $\kappa$  dielectric films on MoS<sub>2</sub>.<sup>35</sup> It should also be noted that the substrate upon which a MoS<sub>2</sub> monolayer is supported will also impact the nucleation and growth behaviours of ALD-dielectric films.<sup>40</sup> Interaction between the substrate and 1L MoS<sub>2</sub> influences the adsorption of reactants, yielding substrate-dependent variation in dielectric film morphology. In this study, we focus on 1L MoS<sub>2</sub> on SiO<sub>2</sub>/Si.

Atomic force microscopy (AFM) is a powerful method for the characterisation of surface morphology. McDonnell *et al.* have previously utilised AFM imaging to estimate a vertical GPC of ~0.1 nm for the direct thermal ALD of HfO<sub>2</sub> on multi-layer (ML) MoS<sub>2</sub> prepared *via* mechanical exfoliation.<sup>25</sup> Similarly, Zhang *et al.* monitored the thickness dependence of the morphology of Al<sub>2</sub>O<sub>3</sub> films grown directly on synthetic polycrystalline ML MoS<sub>2</sub>.<sup>35</sup> The authors evaluated both the lateral and vertical growth rates of ALD-Al<sub>2</sub>O<sub>3</sub> on ML MoS<sub>2</sub> *via* scanning electron microscopy (SEM) and AFM, respectively. However, knowledge of the processes that underpin the formation of high- $\kappa$  dielectric layers on synthesised TMDC monolayers remains limited.<sup>41</sup> CVD has emerged as a leading method for the generation of large-area, high-quality 1L MoS<sub>2</sub> films.<sup>42–47</sup> CVD-MoS<sub>2</sub> is typically polycrystalline, with the lateral dimensions and orientation of the grains, together with the surface coverage, all sensitive to the CVD growth conditions.<sup>48</sup> CVD-grown 1L MoS<sub>2</sub> is known to contain numerous structural defects, including mono- and bi-sulfur vacancies, grain boundaries, impurities, dislocations, and anti-sites.<sup>49,50</sup> The morphology of a 1L MoS<sub>2</sub> surface prepared *via* CVD will influence subsequent ALD of a dielectric.<sup>38</sup> With large-area 1L MoS<sub>2</sub> increasingly synthesised by CVD methods, an assessment of the direct ALD of high- $\kappa$  dielectrics on CVD-grown 1L MoS<sub>2</sub> is critical for future device integration.

In this work, we employ both low- and high-magnification AFM to study nucleation and growth behaviours of direct thermal ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> on SiO<sub>2</sub>/Si-supported CVD-1L MoS<sub>2</sub> films. By systematically examining the physical properties of the deposited dielectric films as a function of the number of ALD cycles, we elucidate the vertical and lateral GPCs associated with each deposition. We also assess the impact of the deposited films on the optical properties of CVD-1L MoS<sub>2</sub> *via* Raman and photoluminescence (PL) spectroscopies.

## Experimental

### Materials

1 cm × 1 cm undoped hexagonal phase 1L MoS<sub>2</sub> films (>99%) grown on SiO<sub>2</sub>/Si *via* atmospheric pressure chemical vapour deposition (APCVD) were supplied by 2D Semiconductors.<sup>42</sup> Each film was cleaved into at least nine smaller samples of approximately equal size. The films were supplied in vacuum-



sealed packaging and cleaved samples were stored in a desiccator to alleviate any degradation effects due to ambient exposure.<sup>51</sup> The monolayer nature of the MoS<sub>2</sub> samples was verified *via* AFM imaging and Raman mapping measurements, as described in section S1 of the ESI.† Companion polished SiO<sub>2</sub>/Si wafers were rinsed in deionised water and then dipped in ~2–3% hydrofluoric acid (HF) for ~1 min to remove the top few nm of oxide immediately before ALD of Al<sub>2</sub>O<sub>3</sub> or HfO<sub>2</sub>.

### High- $\kappa$ dielectric deposition

Thermal ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> was performed at 200 °C using a Veeco Fiji G2 system. All depositions used water (H<sub>2</sub>O) as the co-reactant and argon (Ar) was employed as both the carrier and purging gas. Al<sub>2</sub>O<sub>3</sub> was grown by pulsing trimethylaluminium (TMA) precursor for 0.06 s, and H<sub>2</sub>O for 0.06 s, purging for 8 s between each step. To deposit HfO<sub>2</sub> films, a tetrakis(dimethylamido)hafnium (TDMAH) precursor, heated to 75 °C, was pulsed for 0.25 s, followed by 0.06 s of H<sub>2</sub>O, with an 8 s purge step before and after each pulse. For all depositions of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> in this study, the precursor delivery lines were heated to 150 °C.

### Atomic force microscopy

Surface topographies were imaged *via* AFM using a Bruker Dimension Icon in the PeakForce Tapping Mode and a ScanAsystAir tip (with a nominal tip length of 115  $\mu\text{m}$ , a tip radius of 2 nm, and a spring constant of 0.4 N m<sup>-1</sup>).<sup>52</sup> All AFM images comprised 256 lines per scan and were acquired at a scan rate of 0.5 Hz to yield an appropriate resolution. The Gwyddion 2.60 software package was used for image processing and analysis.<sup>53</sup> The surface coverage of the ALD-dielectric films was estimated using the Fiji distribution of the ImageJ software package, by converting the AFM maps to 8-bit grayscale and subsequently binary images *via* the software's thresholding algorithm.<sup>54</sup>

### Raman and PL spectroscopy

Raman and PL data were acquired at room temperature using a Renishaw inVia Reflex Raman microscope in standard confocal mode with a 532 nm excitation laser at 0.1% of maximum power (~0.18  $\mu\text{W}$ ). A Leica 50 $\times$  objective lens was used, with a numerical aperture of 0.75 and a grating with 1800 lines per mm. Optical micrographs of the samples were acquired with this optical configuration. Single-spot Raman data were the sum of 4 accumulations of 5 s each, with the corresponding PL data the sum of 4 accumulations of 10 s each. Multipeak Lorentzian fitting of single-spot PL spectra was performed, with the exciton and trion peak energies constrained within approximate initial estimates and their linewidths allowed to vary freely. Raman and PL mapping data were also obtained for each sample, collected over an area of 12  $\mu\text{m} \times 12 \mu\text{m}$  with a step size of 0.5  $\mu\text{m}$ . Each PL map was centred around ~1.85 eV and the spectrum at each point fitted with a single Lorentzian curve, with the peak intensity extracted and mapped as a function of position. Similarly, a superposition of two Lorentzian functions was fitted to each

Raman spectrum to encompass the two characteristic MoS<sub>2</sub> peaks. The exposure conditions used to acquire PL/Raman spectra following ALD were identical to those used to measure the corresponding untreated MoS<sub>2</sub>. All data were recorded *via* the Renishaw WiRE 3.1 software package with cosmic-ray features eliminated where necessary.

### Spectral reflectivity

The thicknesses of HfO<sub>2</sub> films grown on MoS<sub>2</sub>-free companion SiO<sub>2</sub>/Si wafers were determined *via* spectral reflectance measurements using a Filmetrics F40-UV microscope. The relative uncertainty of the F40-UV system is  $\pm 1 \text{ nm}$ ,<sup>55,56</sup> and a SiO<sub>2</sub>/Si reference wafer with known SiO<sub>2</sub> thickness was used to calibrate the system. Average thickness was determined from at least five points randomly distributed across the sample. A three-variable model in FILMeasure 9 software was utilised to determine the dielectric film thicknesses from the measured reflectance spectra.<sup>57</sup>

## Results and discussion


### Development of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> films on CVD-1L MoS<sub>2</sub>

We first discuss the nucleation and growth of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> on CVD-grown 1L MoS<sub>2</sub> films by varying the number of ALD cycles, from 25 cycles to 200 cycles. Each deposition was performed on a separate cleaved 1L MoS<sub>2</sub> sample. Select high-magnification AFM images of the dielectric film and approximated maps of the dielectric surface coverage associated with each deposition explored here are presented in Fig. 1 (Al<sub>2</sub>O<sub>3</sub>) and Fig. 2 (HfO<sub>2</sub>), with a representative line profile traced across each image.


From the high-magnification AFM images, we evaluate the development of the high- $\kappa$  dielectric films on 1L MoS<sub>2</sub>. By imaging a scan area on the order of a few hundred nanometres, AFM enables visualisation of the dielectric film morphology. As shown in Fig. 1 and 2, the ALD-Al<sub>2</sub>O<sub>3</sub> and ALD-HfO<sub>2</sub> films grown at all cycle numbers comprise nanoscale island structures. Such island morphology has been reported previously for ALD-grown dielectric films on MoS<sub>2</sub>.<sup>22,25,58</sup> The vertical dimension of the island features can be extracted by tracing line profiles across the acquired AFM images, and monitored as the number of ALD cycles increases to ultimately estimate the vertical GPC associated with each deposition. We also track evolution of the lateral dimension of these island features, facilitating evaluation of the lateral GPC. While representative AFM images are displayed in Fig. 1 and 2, island heights and diameters were averaged from at least three high-magnification AFM images obtained from different regions of each 1L MoS<sub>2</sub> sample.

The shape of the Al<sub>2</sub>O<sub>3</sub> island features deposited at each number of cycles can be generalised as a cylinder with a hemisphere on top, as shown in Fig. S2 in the ESI.† After 25 cycles, the ALD-Al<sub>2</sub>O<sub>3</sub> coverage is sparse, covering less than half of the underlying 1L MoS<sub>2</sub> and indicating nucleation predominantly occurs at defective sites and is limited on the basal plane.<sup>35</sup>



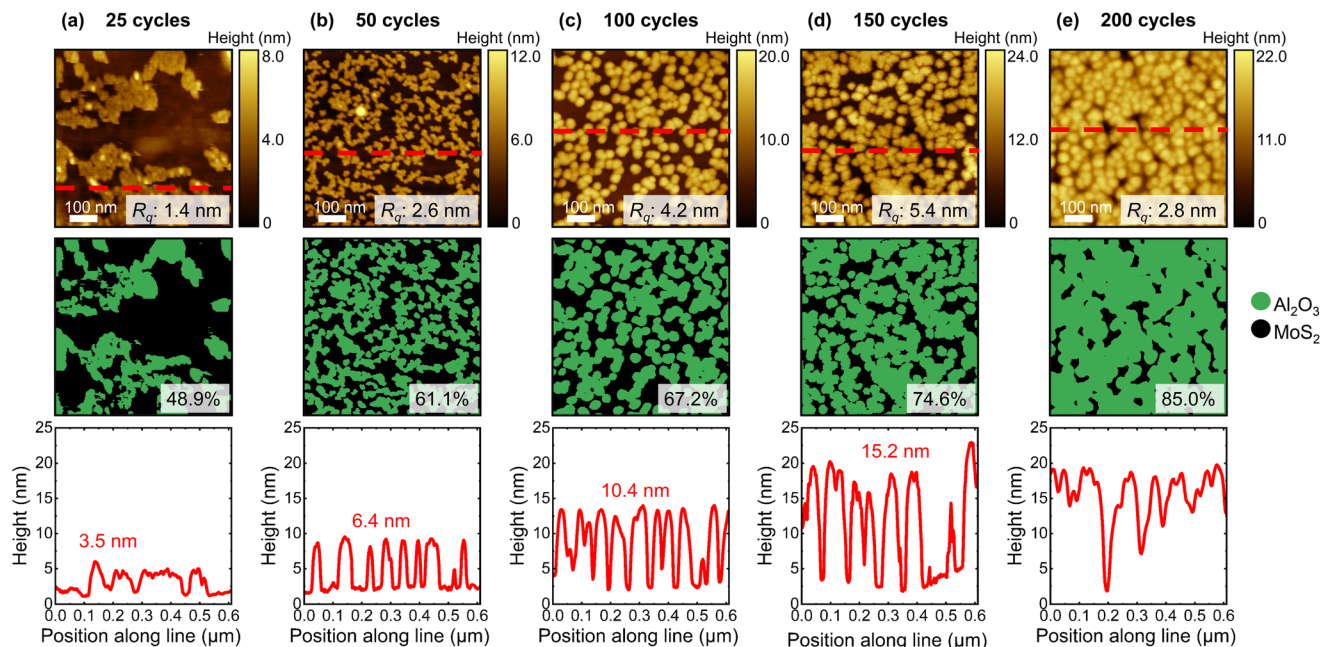

**Fig. 1** High-magnification AFM images (top), maps of estimated surface coverage (middle) and representative line profiles (bottom) of the ALD- $\text{Al}_2\text{O}_3$  films grown on 1L  $\text{MoS}_2$  at cycle numbers (a) 25, (b) 50, (c) 100, (d) 150, and (e) 200. The line profiles were traced along the red dashed lines in each AFM image and the average island height is indicated on the bottom row where applicable – the significant coalescence at 200 ALD cycles prevents evaluation of the island height so no value is quoted in the bottom panel of (e).

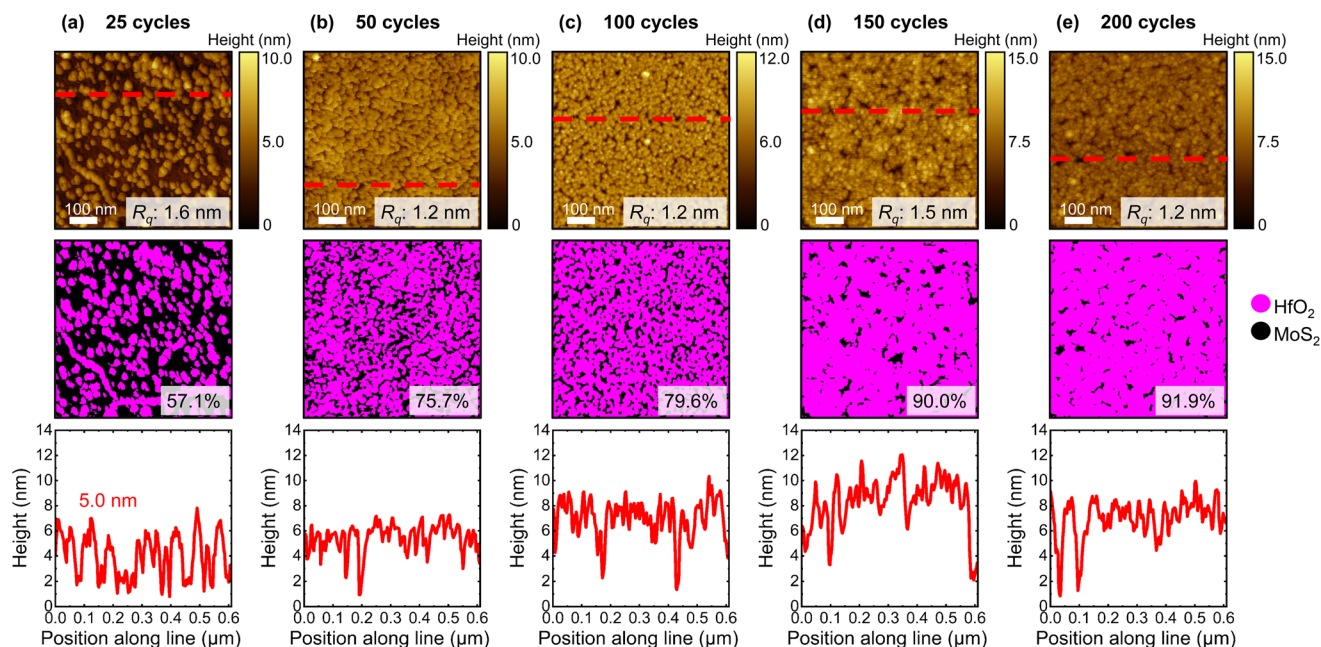

**Fig. 2** High-magnification AFM images (top), maps of estimated surface coverage (middle) and representative line profiles (bottom) of the ALD- $\text{HfO}_2$  films grown on 1L  $\text{MoS}_2$  at cycle numbers (a) 25, (b) 50, (c) 100, (d) 150, and (e) 200. The line profiles were traced along the red dashed lines in each AFM image and the average island height is indicated in (a).

We estimate the average island height to be  $\sim 3.5$  nm and the average diameter as  $\sim 10.3$  nm. The relatively small  $\text{Al}_2\text{O}_3$  structures are packed together in randomly distributed larger “clusters”. The degree of coalescence within each  $\sim 100$  nm-wide

“cluster” is high, but no  $\text{Al}_2\text{O}_3$  islands exist outside of these regions. The ALD- $\text{Al}_2\text{O}_3$  film grown after 50 cycles exhibits a different morphology. Here, the  $\text{Al}_2\text{O}_3$  features do not form “clusters” but are arranged in a network of irregular shapes




and are slightly larger, with an average diameter of  $\sim 24.0$  nm and an average height of  $\sim 6.4$  nm. The increased height of the  $\text{Al}_2\text{O}_3$  features gives a larger root mean square (RMS) surface roughness,  $R_q$ , of 2.6 nm. The  $R_q$  value will be influenced by both the height of the islands and the degree of coalescence, with more continuous films giving smoother  $R_q$  values. The surface coverage after 50 cycles is greater than that after 25 cycles, with  $\sim 61\%$  of the  $\text{MoS}_2$  surface covered by  $\text{Al}_2\text{O}_3$ . We find that after 100 cycles of ALD of  $\text{Al}_2\text{O}_3$ , the dielectric film has an increased surface coverage of  $\sim 67\%$  and comprises a more regular array of larger islands that are  $\sim 10.4$  nm high and  $\sim 27.5$  nm in diameter. The increased vertical dimension of the  $\text{Al}_2\text{O}_3$  islands increases the surface roughness of the film, with  $R_q \sim 4.8$  nm. Following 150 ALD cycles, we find the  $\text{Al}_2\text{O}_3$  film covers  $\sim 75\%$  of the underlying  $\text{MoS}_2$  surface, with  $R_q \sim 5.4$  nm. The dimensions of the  $\text{Al}_2\text{O}_3$  islands are again increased; we evaluate the average height to be  $\sim 15.2$  nm and the average diameter to be  $\sim 30.5$  nm. Even after 200 cycles, the ALD- $\text{Al}_2\text{O}_3$  film does not develop *via* layer-by-layer growth, but rather comprises island features that are, on average,  $\sim 32.9$  nm in diameter and cover  $\sim 89\%$  of the  $\text{MoS}_2$  surface. The enhanced surface coverage results from a greater degree of coalescence, but complete coverage is not achieved even after 200 ALD cycles. The closer packing of the dielectric islands means the AFM tip cannot always access the uncovered  $\text{MoS}_2$  regions between islands, making accurate evaluation of the island height in this sample challenging. The representative line profile extracted from the  $\text{Al}_2\text{O}_3$  film after 200 cycles, as displayed in Fig. 1e, shows relatively small variations in height and is relatively smooth ( $R_q \sim 2.8$  nm). However, in some regions of the film, a sufficient number of  $\text{Al}_2\text{O}_3$  islands are isolated from their neighbours (see Fig. S3 in the ESI†) and we estimate the island height as  $\sim 20.3$  nm.

Compared to the hemispherically-capped cylindrical nanostructures seen in the  $\text{Al}_2\text{O}_3$  films, islands observed in the  $\text{HfO}_2$  films displayed in Fig. 2 are more conical in shape at all ALD cycle numbers (Fig. S2†). This difference in shape may result from the bulkier size of the TDMAH precursor compared to TMA.<sup>37</sup> Dense nucleation along a  $\text{MoS}_2$  grain boundary is

evident after 25 cycles of  $\text{HfO}_2$  (Fig. 2a), but  $\text{HfO}_2$  islands, though more sparsely arranged, are also observed on the  $\text{MoS}_2$  basal plane. Following 25 ALD cycles, the conical islands in the ALD- $\text{HfO}_2$  film have an average base diameter of  $\sim 25$  nm, an average height of  $\sim 5$  nm, and cover  $\sim 57\%$  of the underlying  $\text{MoS}_2$ . From 50 ALD cycles onwards, the continuity of the ALD- $\text{HfO}_2$  films increases with cycle number, with over 90% surface coverage achieved after 200 cycles.

In general, as shown in Fig. 3, we find that as the number of ALD cycles increases, the island features in the deposited  $\text{Al}_2\text{O}_3$  film expand in both the lateral and vertical directions, and the surface coverage of the film increases. Moreover, the roughness of the deposited  $\text{Al}_2\text{O}_3$  films increases up to 150 cycles, with increased coalescence at 200 cycles yielding a smoother morphology. With growth proceeding both vertically and laterally, it is clear that ALD- $\text{Al}_2\text{O}_3$  films develop on CVD-1L  $\text{MoS}_2$  *via* a 3D growth mode. Lateral expansion during island growth has been reported to occur during the second ALD half-cycle.<sup>59</sup> We find that from 50 ALD cycles onwards, the height and diameter of the  $\text{Al}_2\text{O}_3$  islands evolve linearly. As has been described for substrate-inhibited ALD,<sup>41,59</sup> including ALD of  $\text{Al}_2\text{O}_3$  on synthetic ML  $\text{MoS}_2$ ,<sup>35</sup> we separate the development of ALD- $\text{Al}_2\text{O}_3$  on CVD-1L  $\text{MoS}_2$  observed here into a three-stage growth process: (i) initial nucleation from 0 to 25 cycles, (ii) transition regime from 25 to 50 cycles, and (iii) linear growth mode after 50 cycles. In the initial regime, the inert basal plane of CVD-1L  $\text{MoS}_2$  impedes ALD, resulting in a low nucleation density, with nucleation likely occurring only at defects and grain boundaries. As island coalescence accelerates, the surface roughness, surface coverage, and  $\text{Al}_2\text{O}_3$  island dimensions increase quickly in the transition regime until linear growth with a constant GPC is achieved. From the linear cycle dependences of island height and diameter after 50 cycles, we estimate the vertical GPC of this thermal ALD growth of  $\text{Al}_2\text{O}_3$  on CVD-1L  $\text{MoS}_2$  to be  $0.09 \pm 0.01$  nm, with a lateral GPC of  $0.06 \pm 0.01$  nm.

Overall, we reveal the degree of coalescence of the ALD- $\text{HfO}_2$  films is greater than that of the ALD- $\text{Al}_2\text{O}_3$  films, for all number of cycles (Fig. 3c). This indicates improved nuclea-

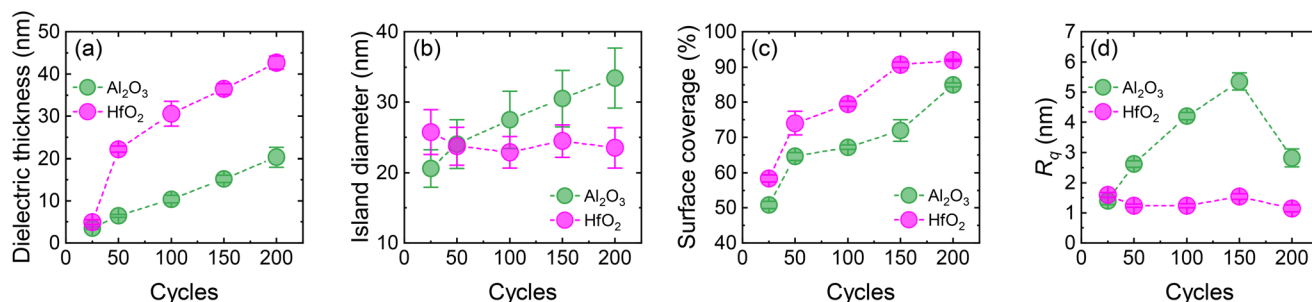

**Fig. 3** Comparisons of the cycle dependence of the average (a) dielectric film thickness, (b) island diameter, (c) surface coverage, and (d)  $R_q$  values of the ALD- $\text{Al}_2\text{O}_3$  (green) and ALD- $\text{HfO}_2$  (magenta) films. The error bars indicate one standard deviation. In (a), the plotted thickness corresponds to the island height for all ALD cycles of  $\text{Al}_2\text{O}_3$  and for 25 ALD cycles of  $\text{HfO}_2$ . For depositions of  $\text{HfO}_2$  beyond 25 cycles, the thickness plotted in (a) is the inferred thickness obtained from lower-magnification AFM images and spectral reflectivity measurements on companion  $\text{MoS}_2$ -free  $\text{SiO}_2/\text{Si}$  wafers, as described in the main text and section S4 of the ESI.†



tion and growth characteristics result from the TDMAH/MoS<sub>2</sub> and/or TDMAH/H<sub>2</sub>O interactions than from those involving TMA. The physisorption of bulkier ALD precursor molecules on MoS<sub>2</sub> has been reported to be more energetically favourable.<sup>60</sup> Compared to the reaction with TMA, an enhanced interaction between MoS<sub>2</sub> and TDMAH may contribute to an improved nucleation pattern that facilitates the higher surface coverage observed at all cycle numbers for HfO<sub>2</sub>. Whereas the diameter of the Al<sub>2</sub>O<sub>3</sub> islands and the associated surface roughness varies with the number of ALD cycles, we find the island diameter and roughness of the HfO<sub>2</sub> films show no cycle dependence, as plotted in Fig. 3b and d. This suggests the development of ALD-HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub> does not proceed *via* the same 3D growth mode as Al<sub>2</sub>O<sub>3</sub>, with only vertical growth occurring with further ALD cycles. With no appreciable lateral expansion of HfO<sub>2</sub> islands, we suggest that the increased surface coverage of the HfO<sub>2</sub> films at a higher number of ALD cycles originates from the formation of new islands.

The significant degree of coalescence in ALD-HfO<sub>2</sub> observed for all depositions of more than 25 ALD cycles prevents evaluation of the vertical GPC from the high-magnification AFM images as performed for ALD-Al<sub>2</sub>O<sub>3</sub>, since there are no isolated HfO<sub>2</sub> islands. To estimate the vertical GPC of ALD-HfO<sub>2</sub>, we instead utilise lower-magnification AFM imaging and the thickness of HfO<sub>2</sub> deposited on companion SiO<sub>2</sub>/Si wafers measured *via* spectral reflectivity. We trace line profiles across relatively low-magnification AFM scans of areas close to the edges of each HfO<sub>2</sub>-encapsulated 1L MoS<sub>2</sub> film, where bordering SiO<sub>2</sub>/Si substrate regions are adjacent to obtain the step height between HfO<sub>2</sub>/MoS<sub>2</sub> and HfO<sub>2</sub>/SiO<sub>2</sub>/Si. By imaging a scan area of ~10 μm × 10 μm, we extract line profile information over a relatively large region. The thickness of HfO<sub>2</sub> on MoS<sub>2</sub> is then estimated by subtracting the thickness of CVD-1L MoS<sub>2</sub> (~0.7 nm)<sup>5,61</sup> and the step height from the measured thickness of HfO<sub>2</sub> on SiO<sub>2</sub>/Si.<sup>62</sup> Details of this process are provided in section S4 of the ESI.† The resulting inferred thickness of ALD-HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub> is plotted as a function of ALD cycle number in Fig. 3a. We again assign the initial nucleation stage from 0 to 25 cycles, with a transition regime between 25 and 50 cycles, and linear growth from 50 cycles onwards. From the linear relationship after 50 ALD cycles, we estimate a vertical GPC of ~0.14 ± 0.01 nm, indicating the vertical growth rate of ALD-HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub> is notably faster than that of ALD-Al<sub>2</sub>O<sub>3</sub>. For the same number of thermal ALD cycles, the thickness of HfO<sub>2</sub> grown on CVD-1L MoS<sub>2</sub> is greater than that of Al<sub>2</sub>O<sub>3</sub>. Moreover, our estimated vertical GPC of HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub> (after 50 cycles) is comparable to that previously determined for the growth of HfO<sub>2</sub> on n-type Si *via* an identical thermal ALD process.<sup>63</sup>

At all cycle numbers of ALD-HfO<sub>2</sub>, the island diameter is estimated to be ~25 nm, smaller than the diameter of the ALD-Al<sub>2</sub>O<sub>3</sub> islands deposited at all cycle numbers greater than 25 cycles. This is opposite to the trend recently reported by Schilirò *et al.* for direct thermal ALD of thin Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> films on gold-supported 1L MoS<sub>2</sub>, where HfO<sub>2</sub> nanostructures

after 40 ALD cycles were observed to be larger than the corresponding Al<sub>2</sub>O<sub>3</sub> features.<sup>37</sup> There, the authors attributed the increased island size to a lower precursor diffusivity due to the bulky structure of TDMAH compared to TMA. Our differing observations are likely due to differing substrate–MoS<sub>2</sub> interactions in our SiO<sub>2</sub>/Si supported samples, and the lower temperature of our ALD processes.

*Via* AFM image analysis, we have demonstrated that while ALD-Al<sub>2</sub>O<sub>3</sub> and -HfO<sub>2</sub> films grown directly on CVD-1L MoS<sub>2</sub> both comprise nanoscale island features, the underlying growth mechanisms are different. ALD-Al<sub>2</sub>O<sub>3</sub> films develop *via* a 3D island growth mode, with lateral and vertical expansion of the island dimensions observed with increasing ALD cycle number. In contrast, ALD-HfO<sub>2</sub> films grow primarily in the vertical direction, with minimal change to the lateral dimension of the constituent island structures.

### Impact of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> on the optical properties of CVD-1L MoS<sub>2</sub>

We now discuss the optical behaviour of dielectric-encapsulated CVD-1L MoS<sub>2</sub>. We measure the Raman and PL emission from each 1L MoS<sub>2</sub> sample before and after the depositions of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> at the various numbers of ALD cycles. To the best of our knowledge, no rigorous examination of the Raman and PL signals from MoS<sub>2</sub> following ALD of varying thicknesses of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> has been reported. Li *et al.* studied, *via* single-spot optical measurements, the Raman and PL emission from CVD-grown 1L MoS<sub>2</sub> following thermal ALD of several thicknesses of Al<sub>2</sub>O<sub>3</sub> up to ~24 nm.<sup>64</sup> We have previously established that the PL properties of 1L MoS<sub>2</sub> films synthesised *via* CVD are spatially inhomogeneous.<sup>61</sup> Hence, we here apply a robust characterisation process that combines single-site measurements with spatially resolved Raman and PL maps to accurately assess the influence of high-κ dielectric films on the optical behaviour of CVD-1L MoS<sub>2</sub>.

Fig. 4 displays single-spot PL spectra measured from 1L MoS<sub>2</sub> before and after ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> at the various numbers of ALD cycles. Maps of the maximum absolute PL intensity, peak PL energy, and PL FWHM can be found in section S5 of the ESI.† From the single-spot and mapping PL spectra, it is clear that direct thermal ALD of Al<sub>2</sub>O<sub>3</sub> or HfO<sub>2</sub> attenuates, red shifts, and broadens the 1L MoS<sub>2</sub> PL signal to some extent at all ALD cycle numbers explored here.<sup>26</sup> We define an attenuation factor as the ratio of the maximum absolute PL intensity averaged from the untreated MoS<sub>2</sub> PL mapping data to that obtained from the corresponding sample after ALD. An analogous broadening factor is also introduced to evaluate changes to the spectral width. A comparison of the average attenuation factors, shifts, and broadening factors extracted from the PL mapping data is presented in Fig. 5.

We find non-monotonic relations between the number of ALD cycles and the degree of PL attenuation for both Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub>. For each dielectric, the weakest reduction of the PL signal occurs after 200 ALD cycles, with 100 cycles yielding the largest attenuation. Generally, a greater number of ALD cycles of either dielectric gave rise to a larger redshift in the energy of



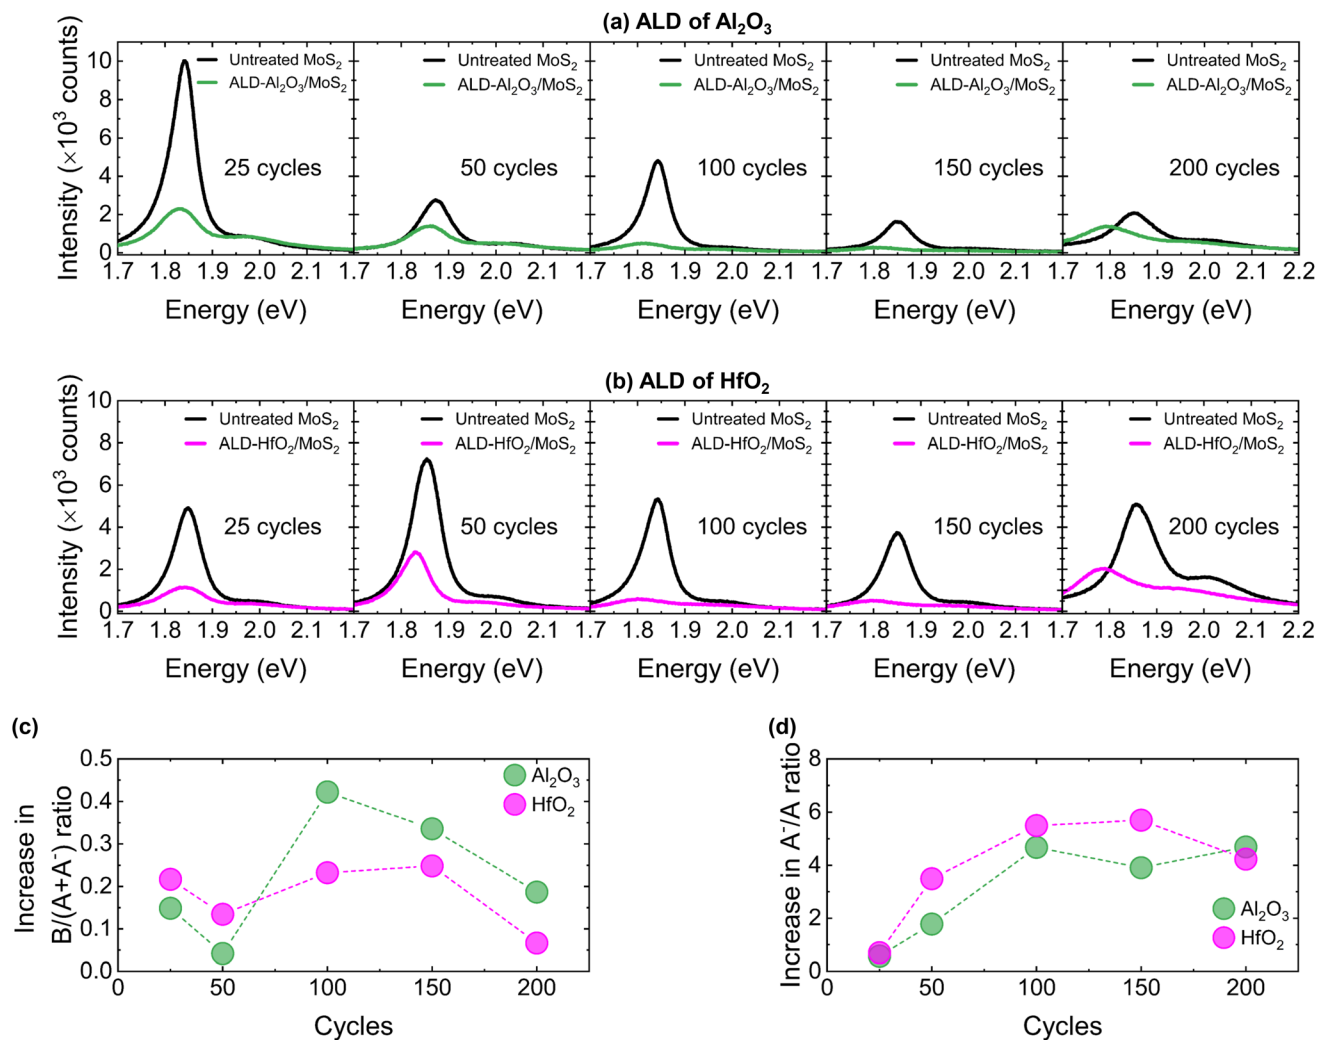


Fig. 4 Single-spot PL spectra measured from each 1L  $\text{MoS}_2$  sample before (black) and after ALD of (a)  $\text{Al}_2\text{O}_3$  (green) and (b)  $\text{HfO}_2$  (magenta) at each number of ALD cycles. Comparison of the changes to the (c)  $B/(A+A^-)$  and (d)  $A^-/A$  intensity ratios induced by each deposition of  $\text{Al}_2\text{O}_3$  and  $\text{HfO}_2$ .

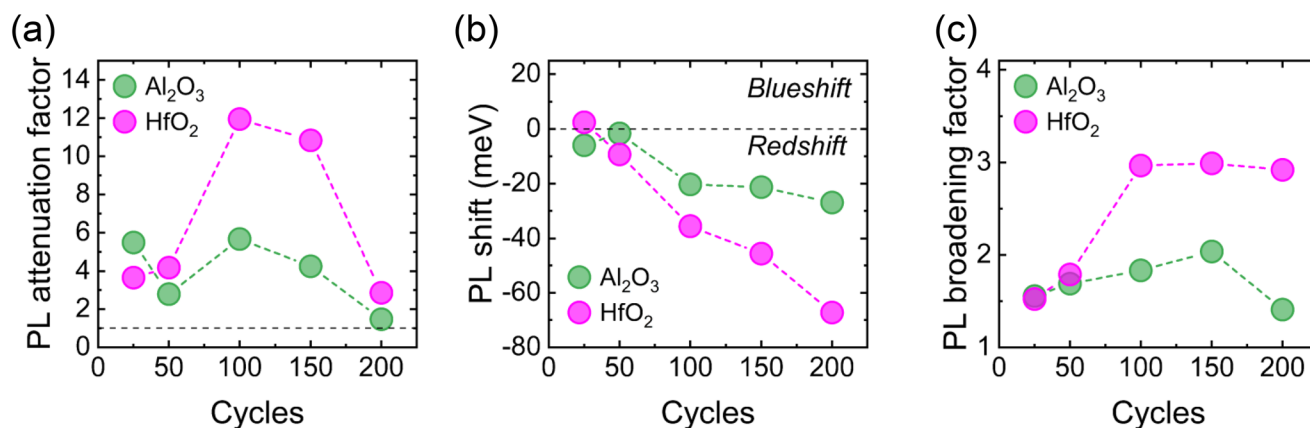


Fig. 5 Comparison of average (a) PL attenuation factors, (b) shifts in PL energy, and (c) PL FWHM broadening factors extracted from the mapping data associated with ALD of  $\text{Al}_2\text{O}_3$  (green) and  $\text{HfO}_2$  (magenta).



the PL emission, with minor shifts (<6 meV) seen at low cycle numbers. Averaged across the mapping data, 25 ALD cycles of HfO<sub>2</sub> resulted in a small blueshift in the PL energy. However, this blueshift may arise from the scatter in the data and, since it is <2 meV, we consider the shift negligible. For more than 50 ALD cycles, the redshift due to ALD-HfO<sub>2</sub> is greater than that induced by ALD-Al<sub>2</sub>O<sub>3</sub>: following 200 ALD cycles of HfO<sub>2</sub>, the peak PL energy is downshifted by ~65 meV, with only a ~25 meV shift after 200 cycles of Al<sub>2</sub>O<sub>3</sub>. For ALD of Al<sub>2</sub>O<sub>3</sub>, the broadening of the MoS<sub>2</sub> PL signal increased with the number of ALD cycles up to 150 cycles, where the deposition broadened the PL linewidth by a factor of ~2. At 200 cycles, ALD of Al<sub>2</sub>O<sub>3</sub> induced a broadening factor of only ~1.4. For ALD of HfO<sub>2</sub>, the PL broadening factor increased up to 100 cycles before remaining constant at ~3× for further cycles.

The attenuated intensity, downshifted energy, and broadened spectral width of the 1L MoS<sub>2</sub> PL emission observed here following ALD of a dielectric material is consistent with previous reports, and such modification of the PL character is thought to originate from the introduction of defects and n-type doping.<sup>26,64–66</sup> A variety of defect states can be created in 1L MoS<sub>2</sub> during thermal ALD of high-κ dielectrics, including sulfur vacancies,<sup>67</sup> charged defects at the dielectric/MoS<sub>2</sub> interface,<sup>68,69</sup> and oxygen substitution at sulfur sites due to exposure to oxidising co-reactants.<sup>33,39</sup> Such defects in 1L MoS<sub>2</sub> act as non-radiative recombination centres and reduce the PL signal strength by trapping photoexcited excitons in mid-bandgap states, thus inhibiting their radiative decay.<sup>70</sup> The creation of defect states can also increase electron-phonon interactions, with the increased disorder in the 1L MoS<sub>2</sub> crystal structure broadening the PL linewidth.<sup>71,72</sup> Since deconvolution of the PL emission can reveal information on both the prevalence of defect states and the electron density in MoS<sub>2</sub>,<sup>73,74</sup> we decompose each single-site PL spectrum obtained before and after ALD into three individual peaks: A and B exciton emissions and an A<sup>-</sup> trion feature. The full deconvoluted spectra associated with the ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> performed in this study are provided in Fig. S8 and S9 in the ESI,† respectively. The ratio of the absolute intensity of the B excitonic PL feature to that of the A exciton has been proposed by McCreary *et al.* as an indicator of defect density in MoS<sub>2</sub>, with a larger ratio corresponding to a more significant abundance of defect states.<sup>73</sup> Since we employ a three-peak fitting of the PL spectra, we define an excitonic ratio as B/(A + A<sup>-</sup>), and the increase in this ratio is plotted as a function of ALD cycle number for both Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> in Fig. 4c. ALD of each dielectric increases the B/(A + A<sup>-</sup>) ratio at all ALD cycle numbers, indicating each deposition introduces defect states in 1L MoS<sub>2</sub>. The trends in the increase in B/(A + A<sup>-</sup>) ratio for each dielectric (Fig. 4c) generally follow the same trajectory as those of the corresponding PL attenuation factor (Fig. 5a), suggesting defect formation is a primary source of dielectric-induced reduction of the 1L MoS<sub>2</sub> PL signal. The maximum increase in B/(A + A<sup>-</sup>) ratio for ALD of both dielectrics occurs at 100 ALD cycles. Beyond 100 cycles, the increase in B/(A + A<sup>-</sup>) ratio becomes less significant as the surface coverage of the

dielectric film increases, and fewer additional defects are created in 1L MoS<sub>2</sub>, particularly at 200 cycles. In general, the change in B/(A + A<sup>-</sup>) ratio induced by ALD of Al<sub>2</sub>O<sub>3</sub> is greater than that following ALD of HfO<sub>2</sub>. We speculate that the enhanced defect formation during Al<sub>2</sub>O<sub>3</sub> deposition may be due to the lateral expansion of islands that does not occur during HfO<sub>2</sub> growth.

In addition to defect generation, n-type doping can also contribute to a reduced, redshifted, and broadened MoS<sub>2</sub> PL signal.<sup>64,74</sup> ALD-grown high-κ dielectrics can modify the electron density in MoS<sub>2</sub> *via* charge transfer at the interface.<sup>39,65,69,75,76</sup> Since the formation of A<sup>-</sup> trions is encouraged by an excess of electrons,<sup>77</sup> the ratio of the absolute intensity of the trionic component to that of the A excitonic feature, A<sup>-</sup>/A, can serve as an indicator of the electron density in MoS<sub>2</sub>.<sup>78</sup> Fig. 4d presents evolution of the A<sup>-</sup>/A ratio with the number of ALD cycles for the growth of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub>. We find that ALD of each dielectric increases the A<sup>-</sup>/A ratio to some extent at all number of ALD cycles, indicating n-type doping of 1L MoS<sub>2</sub>. The enhancement of the A<sup>-</sup>/A ratio increases from 25 to 100 ALD cycles for both dielectrics, before stabilising after 100 cycles. Since the n-type doping of MoS<sub>2</sub> is known to proceed *via* an interfacial transfer of electron density, we suggest that this trend can be attributed to an increase in the number of interfacial sites as further dielectric material is deposited. After 100 cycles, the increased surface coverage of both dielectric films may mean that many interfacial sites are occupied, and further interfacial charge transfer at higher ALD cycle numbers is minimal. The similar magnitude of the increase in A<sup>-</sup>/A ratio for both ALD-Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> at each number of cycles suggests film thickness is not a critical factor in the charge transfer, consistent with an interfacial interaction. In addition to increases in the A<sup>-</sup>/A ratio, the overall progressive redshift of the MoS<sub>2</sub> PL signal observed for increasing ALD cycles of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> may be attributed in part to an increasing redshift in the energy of the A<sup>-</sup> contribution, as shown in Fig. S10 in the ESI.† Despite an apparent general relation between surface coverage and increase in A<sup>-</sup>/A ratio, this intensity ratio may also be impacted by strain and dielectric screening effects. Increasing the dielectric environment of 1L MoS<sub>2</sub> has been reported to enhance and blueshift the PL emission.<sup>78</sup> Since we observe PL attenuation and redshift following all depositions of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub>, we exclude any significant dielectric screening effects. We develop a clearer understanding of the dielectric-induced strain and doping of 1L MoS<sub>2</sub> in the subsequent analysis of the Raman emission.


The distinct Raman spectrum of 1L MoS<sub>2</sub> comprises two characteristic peaks: an in-plane E<sub>2g</sub><sup>1</sup> vibration at ~384 cm<sup>-1</sup> that is sensitive to strain and an out-of-plane A<sub>1g</sub> mode at ~403 cm<sup>-1</sup> that is responsive to charge doping.<sup>79,80</sup> We obtained single-site Raman spectra and spatially resolved maps of the positions and linewidths of the E<sub>2g</sub><sup>1</sup> and A<sub>1g</sub> peaks before and after each ALD of Al<sub>2</sub>O<sub>3</sub> or HfO<sub>2</sub>, and these are provided in section S7 of the ESI.† For growth of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub>, we observe small but appreciable widening of the FWHM of



the 1L MoS<sub>2</sub> Raman peaks at all ALD cycle numbers, with a general increase in the degree of broadening as the cycle number increases (see Fig. S16 in the ESI†). Broadening of the characteristic MoS<sub>2</sub> Raman modes indicates enhanced phonon scattering, typically associated with increased disorder that may arise from the introduction of strain or charge doping.<sup>81</sup> To quantitatively separate the changes in electron density,  $n$ , and mechanical strain,  $\epsilon$ , in CVD-1L MoS<sub>2</sub> induced by each deposition, we employ a correlative analysis previously applied to graphene<sup>82–84</sup> and MoS<sub>2</sub>.<sup>26,37,85–88</sup> Details of this procedure can be found in section S8 of the ESI.† Fig. 6 presents correlative plots of A<sub>1g</sub> peak position as a function of E<sup>1</sup><sub>2g</sub> wavenumber extracted from the Raman mapping data, with overlaid  $\epsilon$ - $n$  grids, for each ALD process studied here. The red dashed

lines correspond to doping isolines and represent  $\Delta n = \pm 0.1 \times 10^{13} \text{ cm}^{-2}$  relative changes in the electron density. A positive (negative)  $\Delta n$  indicates n-type (p-type) doping. Strain isolines are indicated by the black dashed lines and demonstrate variations in the strain of  $\Delta\epsilon = \pm 0.1\%$ .  $\Delta\epsilon > 0$  corresponds to tensile strain, with  $\Delta\epsilon < 0$  representing compressive strain. Comparisons of the doping and strain induced in 1L MoS<sub>2</sub> by ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> at each number of ALD cycles are given in Fig. 6c and d, respectively.

From analysis of the Raman maps, we find thermal ALD of Al<sub>2</sub>O<sub>3</sub> or HfO<sub>2</sub> induces some degree of n-type doping in CVD-1L MoS<sub>2</sub> at all number of cycles, in good agreement with the general changes to the A<sup>-</sup>/A ratio extracted from the single-site PL data. We estimate that 25 cycles of ALD-Al<sub>2</sub>O<sub>3</sub> enhances

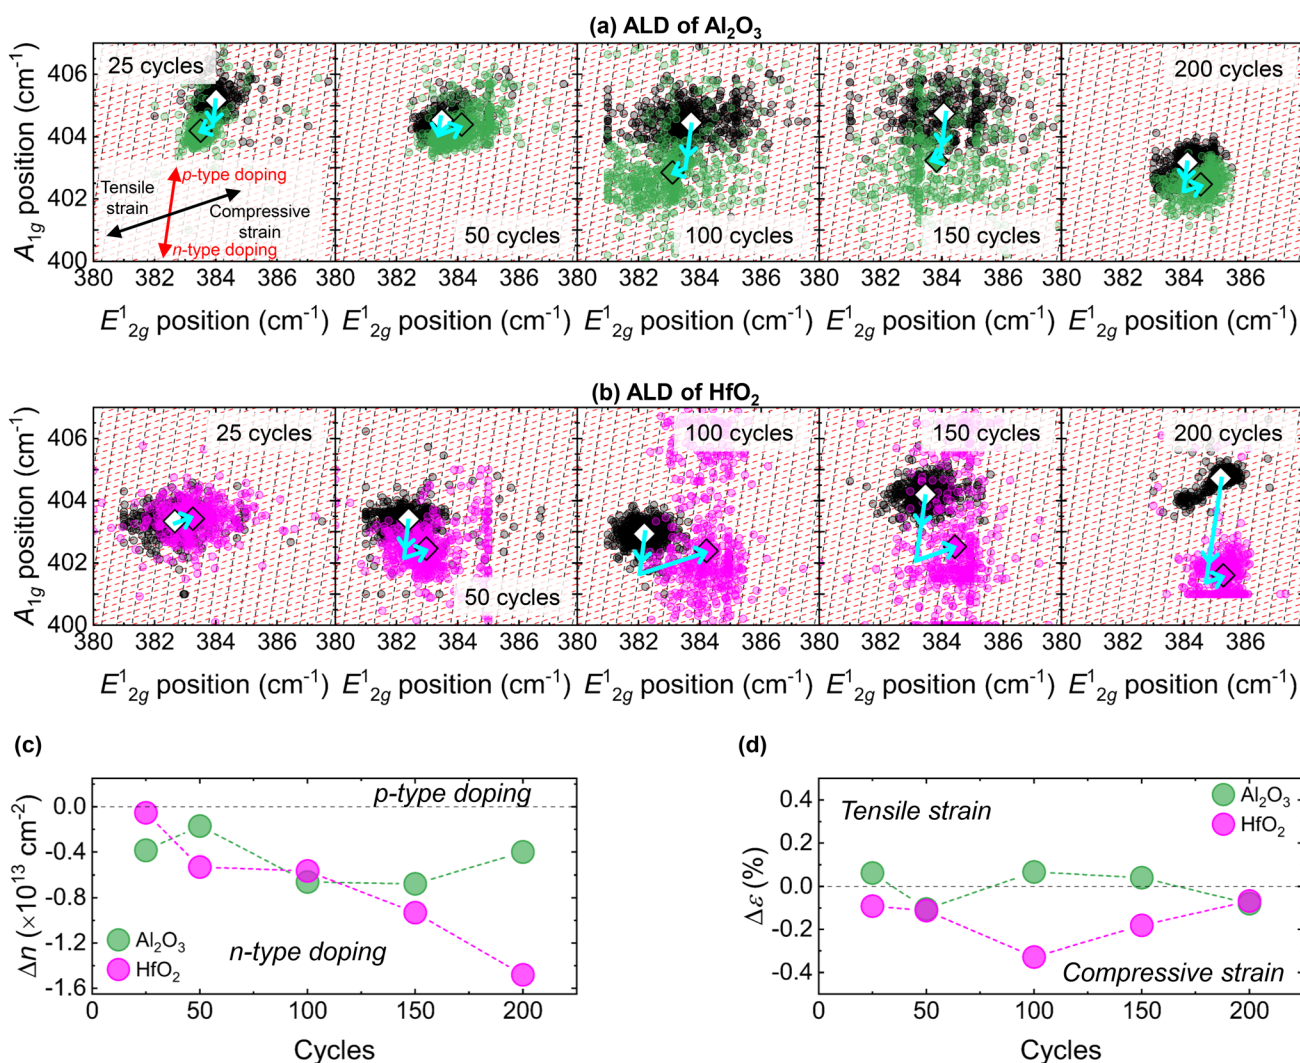

**Fig. 6** Correlative plots of A<sub>1g</sub> and E<sup>1</sup><sub>2g</sub> peak positions extracted from Raman mapping data before (black/white) and after ALD of (a) Al<sub>2</sub>O<sub>3</sub> (green) and (b) HfO<sub>2</sub> (magenta) at each number of ALD cycles. The small circular translucent markers arise from every pixel extracted from the Raman mapping data and the large diamond points indicate the corresponding average values. Strain isolines (black dashed lines) indicate  $\Delta\epsilon = \pm 0.1\%$  variations in the strain and doping isolines (red dashed lines) correspond to relative changes in the electron density of  $\Delta n = \pm 0.1 \times 10^{13} \text{ cm}^{-2}$ . The directions of the strain and doping effects are highlighted in the first panel. Comparison of the average relative changes in (c) electron density,  $\Delta n$ , and (d) mechanical biaxial strain,  $\Delta\epsilon$ , for each deposition.



the MoS<sub>2</sub> electron density by  $\sim 0.4 \times 10^{13} \text{ cm}^{-2}$ , yet only a  $\sim 0.2 \times 10^{13} \text{ cm}^{-2}$  increase results from 50 ALD cycles. The degree of Al<sub>2</sub>O<sub>3</sub>-induced n-type doping reaches a maximum at 100 cycles and 150 cycles, with the electron density of 1L MoS<sub>2</sub> increased by  $\sim 0.7 \times 10^{13} \text{ cm}^{-2}$  following both depositions. At 200 ALD cycles of Al<sub>2</sub>O<sub>3</sub>, the degree of n-type doping is only  $\sim 0.4 \times 10^{13} \text{ cm}^{-2}$ , comparable to that observed after 25 cycles, despite  $\sim 85\%$  surface coverage. The variation in the extent of n-type doping of 1L MoS<sub>2</sub> following ALD of Al<sub>2</sub>O<sub>3</sub> is well explained by the saturation of interfacial sites at increased surface coverage. Due to the lateral component of the 3D growth mode, further Al<sub>2</sub>O<sub>3</sub> film growth after 100 ALD cycles occurs primarily on existing islands rather than directly on uncovered MoS<sub>2</sub>, limiting further charge transfer. For ALD of HfO<sub>2</sub> on CVD-1L MoS<sub>2</sub>, the degree of n-type doping increases monotonically with cycle number up to 200 cycles. With minimal change in the electron density observed after 25 cycles of ALD-HfO<sub>2</sub>, the increase in electron density in 1L MoS<sub>2</sub> is  $\sim 1.5 \times 10^{13} \text{ cm}^{-2}$  after 200 cycles. As the charge transfer occurs at the interfacial region between the ALD-dielectric and 1L MoS<sub>2</sub> surface, the enhanced degree of n-type doping at higher ALD cycle numbers can be explained by the increasing surface coverage and lack of lateral expansion of HfO<sub>2</sub> islands. In addition, a greater doping effect is seen for HfO<sub>2</sub> at higher cycle numbers, where significant dielectric film coalescence is observed. This can be attributed to the higher dielectric constant of HfO<sub>2</sub>: the dielectric constants of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> are  $\sim 8.5$  and  $\sim 20$ , respectively.<sup>89,90</sup> High- $\kappa$  dielectrics alter the local electric field on the MoS<sub>2</sub> surface, thus encouraging electron accumulation at the interface. A higher dielectric constant ALD-film will facilitate stronger interfacial electrostatic interactions and more efficient charge transfer. Moreover, ALD-HfO<sub>2</sub> films are more likely to exhibit oxygen deficiency due to a tendency to form sub-stoichiometric HfO<sub>x</sub> phases, further contributing to n-type doping effects.<sup>39</sup>

The induced changes to strain in 1L MoS<sub>2</sub> due to ALD of Al<sub>2</sub>O<sub>3</sub> are relatively small ( $|\Delta\epsilon| < 0.2\%$ ). The varying degrees of compressive or tensile strain are likely a result of local fluctuations due to the island morphologies and incomplete coalescence of the ALD-Al<sub>2</sub>O<sub>3</sub> films. In contrast, only compressive strain was introduced in 1L MoS<sub>2</sub> following ALD of HfO<sub>2</sub>. A maximum compressive strain ( $\Delta\epsilon \sim -0.3\%$ ) was imparted on MoS<sub>2</sub> after 100 cycles of HfO<sub>2</sub> and we suggest that this is due to localised strain effects from the vertically developing island features. Beyond 100 ALD cycles of HfO<sub>2</sub>, the film coalescence increases such that the strain imparted on the underlying MoS<sub>2</sub> is distributed more evenly and a progressively weaker overall compressive strain effect is seen. We speculate that the relatively modest strain effects observed here in 1L MoS<sub>2</sub> following ALD of Al<sub>2</sub>O<sub>3</sub> or HfO<sub>2</sub> are a result of the physisorption-driven nature of the film nucleation. The resulting vdW interaction between the dielectric and the underlying 1L MoS<sub>2</sub> may limit the efficient transfer of mechanical strain into the monolayer. An exact understanding of the strain effects induced in CVD-1L MoS<sub>2</sub> during ALD of high- $\kappa$  dielectrics requires further research attention.

## Conclusions

We have systematically studied the nucleation and growth of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> films deposited directly on CVD-1L MoS<sub>2</sub> *via* thermal ALD at 200 °C. We have revealed ALD-Al<sub>2</sub>O<sub>3</sub> films develop *via* 3D island growth, with estimated vertical and lateral GPCs of  $0.09 \pm 0.01 \text{ nm}$  and  $0.06 \pm 0.01 \text{ nm}$ , respectively. We find ALD-HfO<sub>2</sub> films also exhibit island morphology, but the absence of lateral expansion indicates the growth of HfO<sub>2</sub> does not evolve *via* the same 3D mode. We attribute the differing growth mechanisms to variations in precursor/1L MoS<sub>2</sub> interactions and nucleation kinetics. We have also investigated the change in the optical behaviour of 1L MoS<sub>2</sub> with differing numbers of ALD cycles of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub>. We find that ALD of Al<sub>2</sub>O<sub>3</sub> and HfO<sub>2</sub> both induce some degree of PL attenuation, redshift, and broadening at all cycle numbers, consistent with defect generation and n-type doping. We connect the modified optical properties of encapsulated 1L MoS<sub>2</sub> to the surface coverage and morphology of the ALD-dielectric films, and rationalise the extent of n-type doping in terms of interfacial charge transfer. This study of the direct ALD of high- $\kappa$  dielectric materials on CVD-1L MoS<sub>2</sub> films has revealed nucleation and growth behaviours that are important for the realisation of 1L MoS<sub>2</sub>-based device structures.

## Author contributions

This study was conceptualised by B. F. M. H. Experimental work was primarily conducted by B. F. M. H., with support from S. L. P. Data analysis was largely performed by B. F. M. H., with discussions and contributions from S. L. P., N. E. G., and J. D. M. The manuscript was written by B. F. M. H., with input and editing from S. L. P., N. E. G., and J. D. M.

## Data availability

Data underpinning figures in this paper can be freely downloaded from <https://wrap.warwick.ac.uk/191653/>. Requests for additional data should be made directly to the corresponding author.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors acknowledge use of Raman/PL facilities within the Spectroscopy Research Technology Platform (RTP), University of Warwick, the AFM facilities within the Electron Microscopy RTP, University of Warwick, and the ALD facilities within the Nano Fabrication RTP, University of Warwick. The Spectroscopy and Electron Microscopy RTPs are part of the



Warwick Analytical Science Centre supported by EPSRC (EP/V007688/1). S. L. P. is supported by a Royal Academy of Engineering Research Fellowship (RF-2324-23-197).

## References

- 1 K. F. Mak, C. Lee, J. Hone, J. Shan and T. F. Heinz, *Phys. Rev. Lett.*, 2010, **105**, 136805.
- 2 A. Splendiani, L. Sun, Y. Zhang, T. Li, J. Kim, C.-Y. Chim, G. Galli and F. Wang, *Nano Lett.*, 2010, **10**, 1271–1275.
- 3 Q. H. Wang, K. Kalantar-Zadeh, A. Kis, J. N. Coleman and M. S. Strano, *Nat. Nanotechnol.*, 2012, **7**, 699–712.
- 4 N. Thomas, S. Mathew, K. M. Nair, K. O'Dowd, P. Forouzandeh, A. Goswami, G. McGranaghan and S. C. Pillai, *Mater. Today Sustainability*, 2021, **13**, 100073.
- 5 J. Jeon, S. K. Jang, S. M. Jeon, G. Yoo, Y. H. Jang, J.-H. Park and S. Lee, *Nanoscale*, 2015, **7**, 1688–1695.
- 6 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, *Nat. Nanotechnol.*, 2011, **6**, 147–150.
- 7 M. Fontana, T. Deppe, A. K. Boyd, M. Rinzan, A. Y. Liu, M. Paranjape and P. Barbara, *Sci. Rep.*, 2013, **3**, 1634.
- 8 A. Pospischil, M. M. Furchi and T. Mueller, *Nat. Nanotechnol.*, 2014, **9**, 257–261.
- 9 M. M. Furchi, A. Pospischil, F. Libisch, J. Burgdörfer and T. Mueller, *Nano Lett.*, 2014, **14**, 4785–4791.
- 10 Y. Zhang, H. Li, L. Wang, H. Wang, X. Xie, S.-L. Zhang, R. Liu and Z.-J. Qiu, *Sci. Rep.*, 2015, **5**, 7938.
- 11 O. Lopez-Sanchez, D. Lembke, M. Kayci, A. Radenovic and A. Kis, *Nat. Nanotechnol.*, 2013, **8**, 497–501.
- 12 M. Nayeri, M. Moradinasab and M. Fathipour, *Semicond. Sci. Technol.*, 2018, **33**, 025002.
- 13 Y. Zhang, J. Ye, Y. Matsushashi and Y. Iwasa, *Nano Lett.*, 2012, **12**, 1136–1140.
- 14 N. Aspiotis, K. Morgan, B. März, K. Müller-Caspary, M. Ebert, E. Weatherby, M. E. Light, C.-C. Huang, D. W. Hewak, S. Majumdar and I. Zeimpekis, *npj 2D Mater. Appl.*, 2023, **7**, 18.
- 15 C. Liu, H. Chen, S. Wang, Q. Liu, Y.-G. Jiang, D. W. Zhang, M. Liu and P. Zhou, *Nat. Nanotechnol.*, 2020, **15**, 545–557.
- 16 S. M. George, *Chem. Rev.*, 2010, **110**, 111–131.
- 17 R. W. Johnson, A. Hultqvist and S. F. Bent, *Mater. Today*, 2014, **17**, 236–246.
- 18 D. J. Hagen, M. E. Pemble and M. Karppinen, *Appl. Phys. Rev.*, 2019, **6**, 041309.
- 19 R. S. Bonilla, B. Hoex, P. Hamer and P. R. Wilshaw, *Phys. Status Solidi A*, 2017, **214**, 1700293.
- 20 M. Leskelä and M. Ritala, *Angew. Chem., Int. Ed.*, 2003, **42**, 5548–5554.
- 21 M. Chhowalla, H. S. Shin, G. Eda, L.-J. Li, K. P. Loh and H. Zhang, *Nat. Chem.*, 2013, **5**, 263–275.
- 22 H. Liu, K. Xu, X. Zhang and P. D. Ye, *Appl. Phys. Lett.*, 2012, **100**, 152115.
- 23 B. J. Chou, Y. C. Chang, W. H. Chang and C. H. Chen, *IEEE J. Electron Devices Soc.*, 2022, **10**, 1033–1039.
- 24 J. Yang, S. Kim, W. Choi, S. H. Park, Y. Jung, M.-H. Cho and H. Kim, *ACS Appl. Mater. Interfaces*, 2013, **5**, 4739–4744.
- 25 S. McDonnell, B. Brennan, A. Azcatl, N. Lu, H. Dong, C. Buie, J. Kim, C. L. Hinkle, M. J. Kim and R. M. Wallace, *ACS Nano*, 2013, **7**, 10354–10361.
- 26 B. F. M. Healy, S. L. Pain, J. Lloyd-Hughes, N. E. Grant and J. D. Murphy, *Adv. Mater. Interfaces*, 2024, **11**, 2400305.
- 27 S. Son, S. Yu, M. Choi, D. Kim and C. Choi, *Appl. Phys. Lett.*, 2015, **106**, 021601.
- 28 X. Zou, J. Wang, C.-H. Chiu, Y. Wu, X. Xiao, C. Jiang, W.-W. Wu, L. Mai, T. Chen, J. Li, J. C. Ho and L. Liao, *Adv. Mater.*, 2014, **26**, 6255–6261.
- 29 B. Huang, M. Zheng, Y. Zhao, J. Wu and J. T. L. Thong, *ACS Appl. Mater. Interfaces*, 2019, **11**, 35438–35443.
- 30 C. Jung, H. I. Yang and W. Choi, *Nanoscale Res. Lett.*, 2019, **14**, 278.
- 31 S. Park, S. Y. Kim, Y. Choi, M. Kim, H. Shin, J. Kim and W. Choi, *ACS Appl. Mater. Interfaces*, 2016, **8**, 11189–11193.
- 32 A. Azcatl, S. McDonnell, S. K. C. X. Peng, H. Dong, X. Qin, R. Addou, G. I. Mordi, N. Lu, J. Kim, M. J. Kim, K. Cho and R. M. Wallace, *Appl. Phys. Lett.*, 2014, **104**, 111601.
- 33 B. F. M. Healy, S. L. Pain, M. Walker, N. E. Grant and J. D. Murphy, *ACS Appl. Nano Mater.*, 2025, **8**, 7334–7346.
- 34 A. Hiraiwa, D. Matsumura and H. Kawarada, *J. Appl. Phys.*, 2016, **120**, 084504.
- 35 H. Zhang, D. Chiappe, J. Meersschaut, T. Conard, A. Franquet, T. Nuytten, M. Mannarino, I. Radu, W. Vandervorst and A. Delabie, *J. Chem. Phys.*, 2016, **146**, 052810.
- 36 K. M. Price, K. E. Schauble, F. A. McGuire, D. B. Farmer and A. D. Franklin, *ACS Appl. Mater. Interfaces*, 2017, **9**, 23072–23080.
- 37 E. Schilirò, S. E. Panasci, A. M. Mio, G. Nicotra, S. Agnello, B. Pecz, G. Z. Radnoczi, I. Deretzis, A. La Magna, F. Roccaforte, R. Lo Nigro and F. Giannazzo, *Appl. Surf. Sci.*, 2023, **630**, 157476.
- 38 J. A. Kropp, Y. Cai, Z. Yao, W. Zhu and T. Gougousi, *J. Vac. Sci. Technol., A*, 2018, **36**, 06A101.
- 39 R. Mahlouji, Y. Zhang, M. A. Verheijen, S. Karwal, J. P. Hofmann, W. M. M. Kessels and A. A. Bol, *ACS Appl. Nano Mater.*, 2024, **7**, 18786–18800.
- 40 E. Schilirò, R. Lo Nigro, F. Roccaforte and F. Giannazzo, *Appl. Sci.*, 2021, **11**, 11052.
- 41 T.-T. Lee, K. Chiranjeevulu, S. Pedaballi, D. Cott, A. Delabie, C.-F. Dee and E. Y. Chang, *J. Vac. Sci. Technol., A*, 2022, **41**, 013201.
- 42 Y.-H. Lee, X.-Q. Zhang, W. Zhang, M.-T. Chang, C.-T. Lin, K.-D. Chang, Y.-C. Yu, J. T.-W. Wang, C.-S. Chang, L.-J. Li and T.-W. Lin, *Adv. Mater.*, 2012, **24**, 2320–2325.
- 43 Y. Yu, C. Li, Y. Liu, L. Su, Y. Zhang and L. Cao, *Sci. Rep.*, 2013, **3**, 1866.
- 44 J. Zhang, H. Yu, W. Chen, X. Tian, D. Liu, M. Cheng, G. Xie, W. Yang, R. Yang, X. Bai, D. Shi and G. Zhang, *ACS Nano*, 2014, **8**, 6024–6030.
- 45 K. Kang, S. Xie, L. Huang, Y. Han, P. Y. Huang, K. F. Mak, C.-J. Kim, D. Muller and J. Park, *Nature*, 2015, **520**, 656–660.



- 46 M. P. C. Taverne, X. Zheng, Y.-S. J. Chen, K. A. Morgan, L. Chen, N. M. Palakkool, D. Rezaie, H. Awachi, J. G. Rarity, D. W. Hewak, C.-C. Huang and Y.-L. D. Ho, *ACS Appl. Opt. Mater.*, 2023, **1**, 990–996.
- 47 A. A. Wibowo, M. Tebyetekerwa, A. D. Bui, F. Kremer, S. Saji, Z. Yin, Y. Lu, D. Macdonald and H. T. Nguyen, *ACS Appl. Electron. Mater.*, 2022, **4**, 5072–5080.
- 48 J. You, M. D. Hossain and Z. Luo, *Nano Convergence*, 2018, **5**, 26.
- 49 J. Hong, Z. Hu, M. Probert, K. Li, D. Lv, X. Yang, L. Gu, N. Mao, Q. Feng, L. Xie, J. Zhang, D. Wu, Z. Zhang, C. Jin, W. Ji, X. Zhang, J. Yuan and Z. Zhang, *Nat. Commun.*, 2015, **6**, 6293.
- 50 W. Zhou, X. Zou, S. Najmaei, Z. Liu, Y. Shi, J. Kong, J. Lou, P. M. Ajayan, B. I. Yakobson and J.-C. Idrobo, *Nano Lett.*, 2013, **13**, 2615–2622.
- 51 J. Gao, B. Li, J. Tan, P. Chow, T.-M. Lu and N. Koratkar, *ACS Nano*, 2016, **10**, 2628–2635.
- 52 K. Xu, W. Sun, Y. Shao, F. Wei, X. Zhang, W. Wang and P. Li, *Nanotechnol. Rev.*, 2018, **7**, 605–621.
- 53 D. Nečas and P. Klapetek, *Open Phys.*, 2012, **10**, 181–188.
- 54 J. Schindelin, I. Arganda-Carreras, E. Frise, V. Kaynig, M. Longair, T. Pietzsch, S. Preibisch, C. Rueden, S. Saalfeld, B. Schmid, J.-Y. Tinevez, D. J. White, V. Hartenstein, K. Eliceiri, P. Tomancak and A. Cardona, *Nat. Methods*, 2012, **9**, 676–682.
- 55 L. G. A. Melo, A. P. Hitchcock, D. Susac, J. Stumper and V. Berejnov, *Phys. Chem. Chem. Phys.*, 2018, **20**, 16625–16640.
- 56 *Filmetrics Inc., Operations Manual for the FILMETRICS F20 Thin-Film Analyzer*, Filmetrics Inc., 7.3.2., 2013.
- 57 *Filmetrics Inc., Taking the Mystery Out of Thin-Film Measurement*, Filmetrics Inc., 2012.
- 58 T. Park, H. Kim, M. Leem, W. Ahn, S. Choi, J. Kim, J. Uh, K. Kwon, S.-J. Jeong, S. Park, Y. Kim and H. Kim, *RSC Adv.*, 2017, **7**, 884–889.
- 59 R. L. Puurunen and W. Vandervorst, *J. Appl. Phys.*, 2004, **96**, 7686–7695.
- 60 I. Cho, J. Yang, S. S. Raya and B. Shong, *Colloid Interface Sci. Commun.*, 2025, **65**, 100823.
- 61 B. F. M. Healy, S. L. Pain, J. Lloyd-Hughes, N. E. Grant and J. D. Murphy, *Mater. Res. Express*, 2024, **11**, 015002.
- 62 T. N. Walter, S. Lee, X. Zhang, M. Chubarov, J. M. Redwing, T. N. Jackson and S. E. Mohney, *Appl. Surf. Sci.*, 2019, **480**, 43–51.
- 63 S. L. Pain, E. Khorani, A. Yadav, T. Niewelt, A. Leimenstoll, B. F. M. Healy, M. Walker, D. Walker, N. E. Grant and J. D. Murphy, *RSC Appl. Interfaces*, 2024, **1**, 471–482.
- 64 Y. Li, X. Li, H. Chen, J. Shi, Q. Shang, S. Zhang, X. Qiu, Z. Liu, Q. Zhang, H. Xu, W. Liu, X. Liu and Y. Liu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 27402–27408.
- 65 S. Y. Kim, H. I. Yang and W. Choi, *Appl. Phys. Lett.*, 2018, **113**, 133104.
- 66 M. Turunen, H. Fernandez, S.-T. Akkanen, H. Seppänen and Z. Sun, *2D Mater.*, 2023, **10**, 045018.
- 67 H. Jung, M. Kim, Y. Lee, G. B. Sim, H. Gu, S. Hong, S. Lee, J. Lee, D. Lee, T. Zou, K. Kang, C. W. Myung, Y.-Y. Noh and J. Kwon, *ACS Nano*, 2025, **19**, 6069–6078.
- 68 S. Kc, R. C. Longo, R. M. Wallace and K. Cho, *ACS Omega*, 2017, **2**, 2827–2834.
- 69 C. J. McClellan, E. Yalon, K. K. H. Smithe, S. V. Suryavanshi and E. Pop, *ACS Nano*, 2021, **15**, 1587–1596.
- 70 H. Wang, C. Zhang and F. Rana, *Nano Lett.*, 2015, **15**, 339–345.
- 71 F. Mujeeb, V. Mahamiya, A. Singh, M. Kothari, A. Chowdhury, A. Shukla and S. Dhar, *Appl. Phys. Lett.*, 2024, **125**, 213103.
- 72 F. Cadiz, E. Courtade, C. Robert, G. Wang, Y. Shen, H. Cai, T. Taniguchi, K. Watanabe, H. Carrere, D. Lagarde, M. Manca, T. Amand, P. Renucci, S. Tongay, X. Marie and B. Urbaszek, *Phys. Rev. X*, 2017, **7**, 021026.
- 73 K. M. McCreary, A. T. Hanbicki, S. V. Sivaram and B. T. Jonker, *APL Mater.*, 2018, **6**, 111106.
- 74 S. Mouri, Y. Miyauchi and K. Matsuda, *Nano Lett.*, 2013, **13**, 5944–5948.
- 75 X. Zhang, Z. Shao, X. Zhang, Y. He and J. Jie, *Adv. Mater.*, 2016, **28**, 10409–10442.
- 76 A. Henning, S. Levashov, C. Qian, T. Grünleitner, J. Primbs, J. J. Finley and I. D. Sharp, *Adv. Mater. Interfaces*, 2023, **10**, 2202429.
- 77 K. F. Mak, K. He, C. Lee, G. H. Lee, J. Hone, T. F. Heinz and J. Shan, *Nat. Mater.*, 2013, **12**, 207–211.
- 78 Y. Lin, X. Ling, L. Yu, S. Huang, A. L. Hsu, Y.-H. Lee, J. Kong, M. S. Dresselhaus and T. Palacios, *Nano Lett.*, 2014, **14**, 5569–5576.
- 79 X. Zhang, X.-F. Qiao, W. Shi, J.-B. Wu, D.-S. Jiang and P.-H. Tan, *Chem. Soc. Rev.*, 2015, **44**, 2757–2785.
- 80 H.-J. Kim, D. Kim, S. Jung, M.-H. Bae, Y. J. Yun, S. N. Yi, J.-S. Yu, J.-H. Kim and D. H. Ha, *J. Raman Spectrosc.*, 2018, **49**, 1938–1944.
- 81 B. Chakraborty, A. Bera, D. V. S. Muthu, S. Bhowmick, U. V. Waghmare and A. K. Sood, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 2012, **85**, 161403.
- 82 T. M. G. Mohiuddin, A. Lombardo, R. R. Nair, A. Bonetti, G. Savini, R. Jalil, N. Bonini, D. M. Basko, C. Galiotis, N. Marzari, K. S. Novoselov, A. K. Geim and A. C. Ferrari, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 2009, **79**, 205433.
- 83 J. E. Lee, G. Ahn, J. Shim, Y. S. Lee and S. Ryu, *Nat. Commun.*, 2012, **3**, 1024.
- 84 E. Schilirò, R. Lo Nigro, S. E. Panasci, F. M. Gelardi, S. Agnello, R. Yakimova, F. Roccaforte and F. Giannazzo, *Carbon*, 2020, **169**, 172–181.
- 85 A. Michail, N. Delikoukos, J. Parthenios, C. Galiotis and K. Papagelis, *Appl. Phys. Lett.*, 2016, **108**, 173102.
- 86 W. H. Chae, J. D. Cain, E. D. Hanson, A. A. Murthy and V. P. Dravid, *Appl. Phys. Lett.*, 2017, **111**, 143106.
- 87 S. E. Panasci, E. Schilirò, G. Greco, M. Cannas, F. M. Gelardi, S. Agnello, F. Roccaforte and F. Giannazzo, *ACS Appl. Mater. Interfaces*, 2021, **13**, 31248–31259.
- 88 E. Schilirò, R. L. Nigro, S. E. Panasci, S. Agnello, M. Cannas, F. M. Gelardi, F. Roccaforte and F. Giannazzo, *Adv. Mater. Interfaces*, 2021, **8**, 2101117.
- 89 Y. Lu, S. Bangsaruntip, X. Wang, L. Zhang, Y. Nishi and H. Dai, *J. Am. Chem. Soc.*, 2006, **128**, 3518–3519.
- 90 M. D. Groner, F. H. Fabreguette, J. W. Elam and S. M. George, *Chem. Mater.*, 2004, **16**, 639–645.

