



Cite this: *Org. Biomol. Chem.*, 2025, **23**, 9123

## Preparation of poly-*N*-(methyl)aminoxy serine polypeptides by NCA ring-opening polymerization for modification with reducing oligosaccharides

Francesco Palmieri,<sup>a</sup> Marlinde Waardenburg,<sup>a</sup> Justyna M. Dobruchowska,<sup>a</sup> Elena Roditis,<sup>a</sup> Tina Vermonden <sup>b</sup> and Geert-Jan Boons <sup>\*a,c</sup>

*N*-Carboxyanhydride (NCA) ring-opening polymerization offers an attractive approach for the construction of polypeptides. Here, we report the synthesis of a serine NCA-functionalized monomer bearing a methylaminoxy group, enabling post-polymerization attachment of complex oligosaccharides via a neo-glycosylation reaction. It provides an attractive alternative to traditional click reactions, allowing direct conjugation of glycans with a free reducing end without requiring a reactive linker or toxic reagents. Enzymatically produced 6-sialyl lactose was efficiently conjugated to the methylaminoxy moieties of the polypeptide. The resulting neo-glycopolymer was analyzed by size-exclusion chromatography (SEC) to determine molecular weight and by diffusion-ordered spectroscopy (DOSY) nuclear magnetic resonance (NMR), which confirmed a high degree of functionalization and a substantial increase in hydrodynamic radius. Glycan attachment proceeds under mild acidic conditions highlighting the versatility of the polypeptide scaffold to yield brush-like glycosylated polypeptides.

Received 16th June 2025,  
Accepted 16th September 2025  
DOI: 10.1039/d5ob00985e

rsc.li/obc

### Introduction

$\alpha$ -Amino acid *N*-carboxyanhydride (NCA) ring-opening polymerization is a versatile methodology for producing polypeptides with tunable properties.<sup>1–4</sup> The attraction of NCA polymerization is that it replicates features of natural polypeptides while maintaining the flexibility to incorporate diverse functional groups. It can be performed under mild conditions and is compatible with a variety of  $\alpha$ -amino acids including those having unnatural functional groups.<sup>4–7</sup> In addition, the ring-opening polymerization allows for control over molecular weight, composition, and architecture enabling the design of sophisticated materials.<sup>2,8–12</sup>

NCA ring opening polymerization has been used to generate highly glycosylated polypeptides that mimic biomolecules such as mucins.<sup>13–15</sup> Two strategies have been pursued to prepare such polymers based on pre- or post-polymerization attachment of carbohydrates.<sup>16</sup> In the first approach, a fully protected glycosylated amino acid is converted into an NCA

and then co-polymerized with other NCA amino acids followed by deprotection.<sup>17</sup> The limitation of this strategy lies in the difficulties of preparing monomers having a complex carbohydrate moiety and its use has been limited to mono- and disaccharides.<sup>18,19</sup> In an alternative strategy, polypeptides are prepared using amino acids having a reactive site chain such as azide, alkyne, alkene or an amine that can be derivatized with a glycan having a complementary reactive group by for example azide-alkyne cycloaddition, thiol-Michael addition or Diels-Alder reaction.<sup>20–22</sup> This approach made it possible to install a greater variety of oligosaccharides,<sup>23</sup> however, it usually involves the introduction of unnatural linkers and modification of the glycans with a suitable reactive group.

Glycosylated polypeptides prepared by NCA have provided selective ligands for various lectins, giving opportunities for targeted drug delivery and diagnostic assay development.<sup>20,21,24,25</sup> Such polymers have also been employed for the development of lysosome-targeting chimaeras (LYTACs) that consist of a monoclonal antibody or small molecule fused to a polypeptide functionalized with mannose-6-phosphate moieties.<sup>26</sup> Glycosylated polypeptides have been used as immunomodulating agents by targeting Dectin-1 and Dectin-2 to activate immune cells.<sup>18</sup> Other applications include glycopolypeptide-containing hydrogels for culturing hepatocytes. This application exploits the sialoglycoprotein receptor of hepatocytes to bind to galactosyl moieties of the hydrogel to increase cell viability, differentiation and proliferation.<sup>25</sup> Furthermore, nanogels containing glucose have been used to encapsulate

<sup>a</sup>Division of Chemical Biology and Drug Discovery, Utrecht Institute for Pharmaceutical Sciences, Utrecht University, Universiteitsweg 99, Utrecht 3584 CG, The Netherlands. E-mail: g.j.p.h.boons@uu.nl

<sup>b</sup>Division of Pharmaceutics, Utrecht Institute for Pharmaceutical Sciences, Utrecht University, 3508 TB Utrecht, The Netherlands

<sup>c</sup>Complex Carbohydrate Research Center and Department of Chemistry, University of Georgia, 315 Riverbend Road, Athens, Georgia 30602, USA.

E-mail: gboons@ccrc.uga.edu



insulin that releases at a rate depending on the concentration of glucose.<sup>27</sup>

Here, we describe the synthesis of a serine derived NCA (**1**) bearing a *tert*-butyloxycarbonyl (Boc) protected *N*-methyl aminoxy moiety. It can readily be polymerized and after removal of the Boc protecting group, the aminoxy containing polypeptide can be modified by reducing complex carbohydrates by oxime ligation. Aminoxy derivatives (oximes) are attractive for bioconjugation and can react with aldehydes and ketones under mild conditions.<sup>28</sup> *N*-Methyl aminoxy containing compounds have been attached to reducing glycans<sup>29–32</sup> to give conjugates preserving the cyclic pyranosyl ring structure of the conjugated saccharide<sup>29,33</sup> Conventional peptide chemistry has been employed to prepare glycopeptides having an *N*-methyl aminoxy moiety for attachment of a variety of different saccharides to give compounds maintaining biological activity.<sup>32,34</sup> These findings motivated us to develop monomer **1** for NCA ring-opening polymerization followed by conjugation of reducing saccharides to give neoglycopolymers for studying biological roles of glycosylation, probing molecular recognition events, and developing multivalent ligands for various biomedical applications (Scheme 1). It makes it possible, for the first time, to modify a polypeptide prepared by NCA with complex glycans without the need for an artificial spacer and the use of toxic reagents.

## Results and discussion


### Design and synthesis of the monomer

We designed a synthetic route for monomer **1** having a Boc-protected aminoxy moiety at the side chain. The *N*-methyl of


the aminoxy functionality ensures preservation of the cyclic structure of the saccharide moiety after conjugation.<sup>35</sup> A Mitsunobu reaction of *N*-trityl-*L*-serine methyl ester with *tert*-butyl hydroxy(methyl)carbamate (**2**), was prepared by a literature procedure,<sup>36</sup> using diisopropyl azodicarboxylate (DIAD) in the presence of triphenyl phosphine gave, after purification by silica gel column chromatography, modified protected amino acid **3**. The trityl protecting group of the  $\alpha$ -amine of **4** was selectively removed using 4% trifluoro acetic acid (TFA) in DCM at 0 °C, which was followed by hydrolysis of the methyl ester employing sodium hydroxide in THF generating compound **4** that was isolated by reverse phase silica gel chromatography. The conversion of **4** into NCA **1** was achieved using a recently reported moisture-tolerant procedure<sup>37</sup> entailing treatment with propylene oxide and triphosgene in THF. The purification of **1** was challenging due to its sensitivity to hydrolysis or unwanted polymerization. Ultimately, compound **1** could be obtained by purification using column chromatography on anhydrous silica gel prepared through oven desiccation (Scheme 2).<sup>38</sup>

### Polymerization and characterization of the polypeptide

Monomer **1** was polymerized using lithium bis(trimethylsilyl) amide (LiHMDS)<sup>12</sup> as initiator in a ratio of 1 : 50 (mol mol<sup>-1</sup> [*I/M*]) in anhydrous DCM for 1.5 h under an atmosphere of argon. In this reaction, the hindered base generates an *N*-terminal carbamate anion that serves as the reactive centre for fast chain propagation (Scheme 3). The resulting polymer (**5**) was precipitated by pouring the reaction mixture into ice cold mixture of PE/Et<sub>2</sub>O (1 : 1 v : v). The polymer was analysed by MALDI-TOF MS and SEC. The molecular weight of the

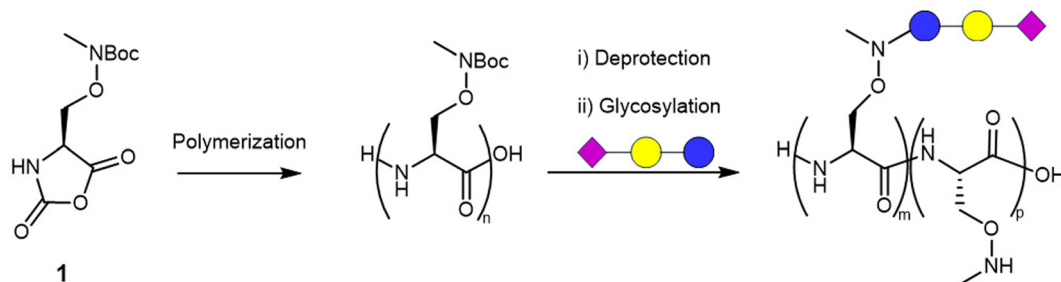


**Scheme 1** General representation of NCA-polymerization of compound **1** to generate a polypeptide-based scaffold that can be glycosylated with free reducing end oligosaccharides.

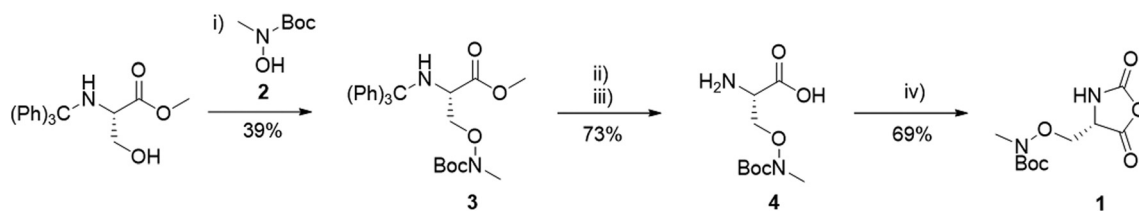

**Scheme 2** *N*-Carboxy anhydride (NCA) monomer synthesis. (i) *N*-Trityl-*L*-serine methyl ester, PPh<sub>3</sub>, DIAD, toluene; (ii) TFA, DCM. (iii) THF/NaOH aq. (0.3 M); (iv) propylene oxide, triphosgene, THF.



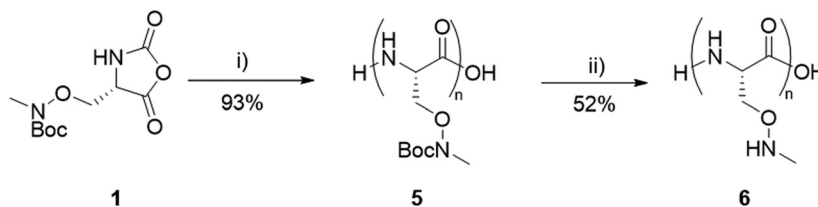


**Scheme 3** i) Polymerization of the monomer (4) using LiHMDS in a ratio 1 : 50 (mol mol<sup>-1</sup> LiHMDS/4) in anhydrous DCM under an argon atmosphere. (ii) Boc deprotection of polymer 5 using TFA/H<sub>2</sub>O (1 : 1).

polymer was determined by SEC to be approximately 15 kDa ( $n \approx 60$ ) with a polydispersity index of 1.06. MALDI-TOF MS showed signals with a difference of +217 Da, which is the molecular weight of the repeating unit of the expected polymer consistent with previously reported MALDI-TOF data of this class of polymers.<sup>12,37</sup> The average molecular weight determined by MALDI-TOF (2571 Da,  $n = 12$ ) is lower than measured by SEC which most likely is due to the higher ionization coefficient of smaller fragments. It is well known that MS underestimates the average molecular weight of this type of polymer.<sup>39</sup> The Boc protecting group of the *N*-methyl aminoxy functionality of the side chain of this polymer was removed using a mixture of TFA (50%) in water (Scheme 2). The deprotected polymer was isolated by size exclusion column chromatography using extra fine polyacrylamide beads (P2 Bio-gel) and ammonium bicarbonate buffer (20 mM) as the eluent. The resulting polymer was characterized by NMR spectroscopy to determine successful Boc deprotection and as expected the NMR signal of Boc ( $\delta$  1.45, 9H) disappeared after the acid treatment of the polymer. Moreover, an upfield shift was observed for the methyl group present on the aminoxy group ( $\delta$  3.08 to  $\delta$  2.58, N-Me, 3H) and the doublet of the beta CH<sub>2</sub> of the amino acid merged into a broad singlet ( $\delta$  3.97, 2H) while the alpha proton is observed at the same chemical shift without

significant variation ( $\delta$ 4.65, 1H) indicating the integrity of the deprotected polymer after acid treatment for Boc deprotection (see SI). Unfortunately, SEC analysis was not possible for the deprotected polymer 6 due to interactions between the polymer and the stationary phase.

#### Ligation of enzymatically synthesized 6-sialyl-lactose

With the fully deprotected polymer 6 in hand, attention was focused on selective ligation of a 6-sialylated lactose (7) having a free reducing end that was synthesized by the reaction of lactose with Cytidine-5'-monophospho-*N*-acetylneuraminic acid (CMP-Neu5Ac) in the presence of the mutated sialyl transferase PmST1 (P34H/M144L)<sup>40</sup> (Scheme 4a). Polymer 6 and Neu5Ac-(2,6)-Lac (7) (1 eq. per aminoxy functionality) were dissolved in a mixture of DMF, H<sub>2</sub>O and acetic acid (1 : 1 : 2, v/v/v) and the resulting solution was agitated for 24 h at 37 °C (Scheme 4b). The glycosylated polymer 8 was purified by P2 Biogel size exclusion chromatography using ammonium bicarbonate (50 mM, pH = 7.4) as the eluent. The resulting glycopolymer was characterized by NMR to determine the successful attachment of the glycan to the polymer and the degree of functionalization. The <sup>1</sup>H NMR and <sup>1</sup>H-<sup>13</sup>C HSQC spectra of glycosylated polymer is depicted in Fig. 1, and the NMR data are given in Table 1. Compared with the spectrum of the non-

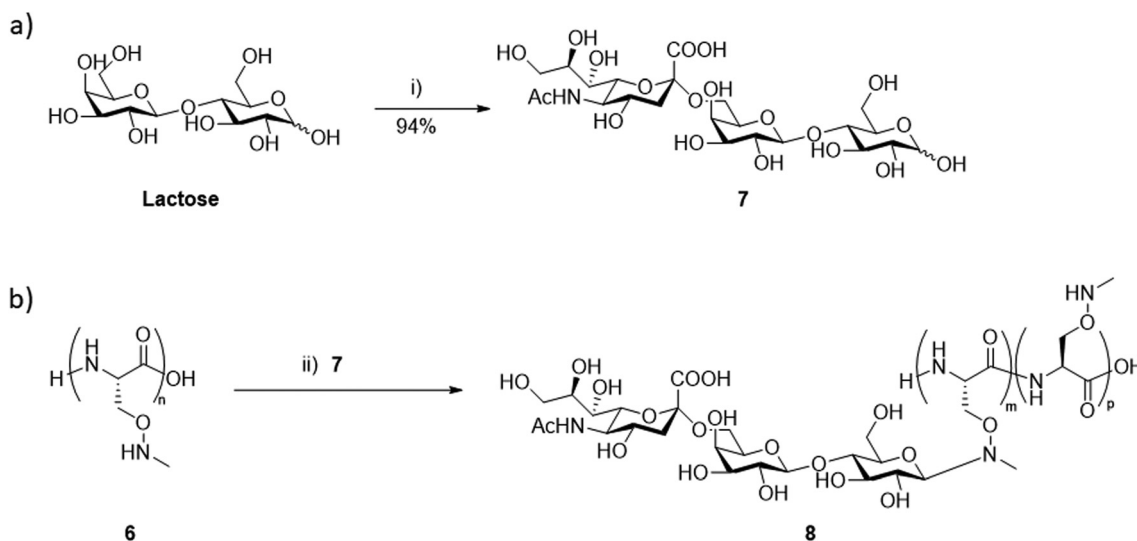

**Scheme 4** a) Enzymatic synthesis of compound 7 using PmST1 (P34H/M144L), lactose, CMP-Neu5Ac in Tris buffer (100 mM pH = 8.5) containing MgCl<sub>2</sub> (20 mM). (b) Neoglycosylation of the polypeptide with oligosaccharide 7 in DMF/H<sub>2</sub>O/AcOH (1 : 1 : 2).



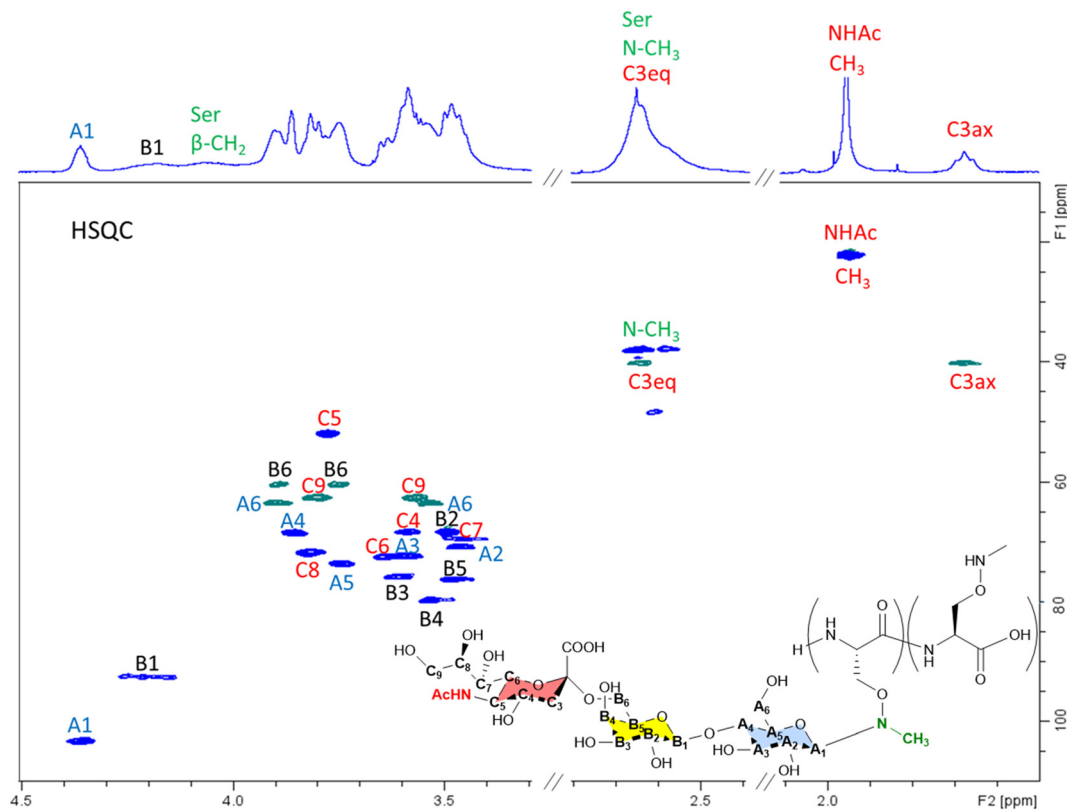


Fig. 1  $^1\text{H}$  NMR and  $^1\text{H}$ - $^{13}\text{C}$  HSQC spectra of glycosylated polymer recorded in  $\text{D}_2\text{O}$  at 298 K. Resonance assignment has been annotated.

Table 1  $^1\text{H}$  and  $^{13}\text{C}$  chemical shifts of glycosylated polymer (**8**) recorded in  $\text{D}_2\text{O}$  at 298 K

Residue	H1/C1	H2/C2	H3/C3	H4/C4	H5/C5	H6/C6	H7/C7	H8/C8	H9/C9	NHAc
Gal	4.36	3.46	3.59	3.86	3.74	3.90, 3.53	—	—	—	—
A	103.3	70.8	72.5	68.6	73.7	63.5	—	—	—	—
Glc	~4.18	3.49	3.61	3.53	3.48	3.89, 3.75	—	—	—	—
B	92.6	68.5	75.8	79.7	76.2	60.4	—	—	—	—
Neu5Ac	—	—	1.68, 2.64	3.59	8.78	3.64	3.46	3.82	3.80, 3.57	1.95
C	174.0	101.3	40.1	68.4	51.9	72.5	69.6	71.9	62.6	22.1
		N-H		$\alpha$ -CH			$\beta$ -CH <sub>2</sub>			N-CH <sub>3</sub>
Ser		7.95		~4.57 n.d.			~4.07 n.d.			~2.64 38.0

glycosylated polymer **6** (Fig. 2), broad signals of  $\beta$ -CH<sub>2</sub> Ser observed at  $\delta \sim 4.07$  have shifted downfield under influence of substitution with Glc (**B**) residues. The widely distribution of  $\beta$ -Glc (**B**) anomeric protons at  $\delta \sim 4.18$  indicates heterogeneity in molecular weight of the glycosylated polymer (Fig. 1). Full assignment of  $\beta$ -Gal (**A**),  $\beta$ -Glc (**B**) and  $\alpha$ -Neu5Ac (**C**) and a partial assignment of Ser was deduced from 2D TOCSY spectra (see SI, Fig. S1a). In the 2D NOESY spectrum the strong inter-residual connectivity (NOE) between H-1's of  $\beta$ -Glc (**B**) and N-CH<sub>3</sub> of Ser, indicate that  $\beta$ -Glc is attached *via* N-linkage to polypeptide backbone (see SI, Fig. S1b). The degree of functionalization was determined by the integration of signals of Ser N-CH<sub>3</sub> and Neu5Ac H-3eq at  $\delta$  2.62 with Neu5Ac H-3ax at  $\delta$  1.68.

The peak area of the well resolved Neu5Ac H-3ax was subtracted from the peak area of Ser N-CH<sub>3</sub>/Neu5Ac H-3eq, giving a degree of functionalization of  $\sim 50\%$ . The use of 1.5 eq. of sialylactose **7** did not result in a notable increase in functionalization, which most likely is due to steric hinderance caused by the already attached glycans.

Glycopolymer **8** was further analyzed and compared to the non-glycosylated polymer **6** and sialyllactose **7** by 2D  $^1\text{H}$ -DOSY NMR, which provides information about the size and shape of molecules.<sup>41,42</sup> As expected, the glycopolymer has a lower diffusion coefficient ( $2.04 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ ) compared to non-glycosylated polymer ( $2.44 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ ) (Fig. 2 and Table 2). The DOSY spectrum of sialyllactose **7** displayed a single set of



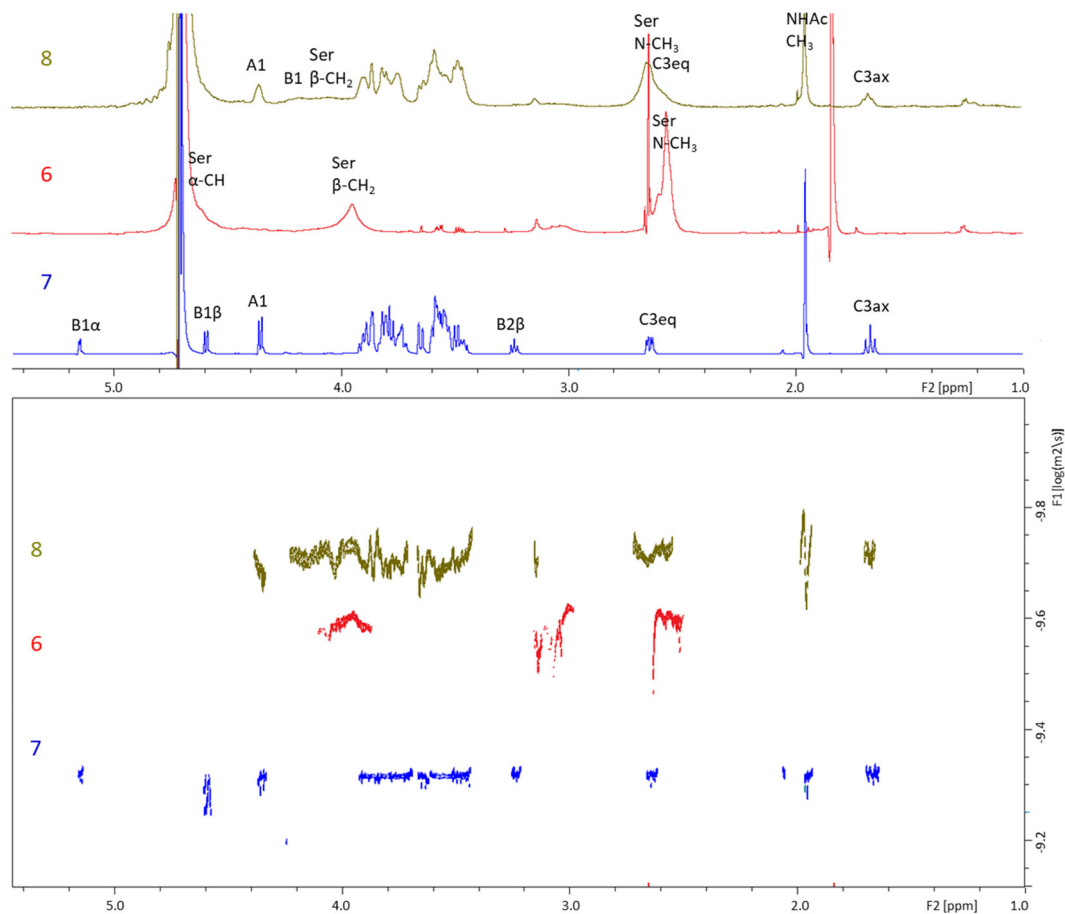


Fig. 2 2D-DOSY NMR of the glycosylated polymer **8**, the non-glycosylated polymer **6**, and sialyllactose **7**.

**Table 2** Diffusion coefficients of the glycosylated polymer **8**, non-glycosylated polymer **6** and sialyllactose **7**, determined by diffusion ordered spectroscopy NMR experiments (2D  $^1\text{H}$ -DOSY-NMR)

Compound	DOSY diffusion coefficient, $D$ ( $\text{m}^2 \text{s}^{-1}$ )
Glycosylated polymer ( <b>8</b> )	$2.04 \times 10^{-10}$
Sialyllactose ( <b>6</b> )	$2.96 \times 10^{-9}$
Non-glycosylated polymer ( <b>7</b> )	$2.44 \times 10^{-10}$

NMR signals (Fig. 2), indicating a single state, in which the molecules behave as a homogeneous unit, leading to a single diffusion coefficient. In contrast, the non-glycosylated polymer **6** and the glycosylated polymer **8**, exhibit dispersed signals, indicating they are in slow exchange and possess a wide range of molecular sizes (polydispersity), which agrees with the MALDI-TOF data. This observation made the analysis of molecular weight by DOSY difficult since polymers often do not follow expected linear trend with respect to molecular weight.<sup>41</sup>

The glycopolymer dissolved well in water, PBS and ammonium bicarbonate buffer (50 mM, pH = 7.4). After an incubation time of 7 days in  $\text{D}_2\text{O}$ , no notable change in the diffusion coefficient was measured by DOSY NMR indicating it had remained intact. It is well established that polypeptides

have good stability under physiological conditions. Furthermore, oximes are stable at pH > 7,<sup>43</sup> which is also the case for sialosides, making the new materials attractive for biomedical applications.

## Conclusions

In this study, we designed, synthesized and characterized an NCA having an appropriately protected aminoxy functionality. LiHMDS-mediated ring opening polymerization yielded a polypeptide that after removal of a Boc protecting group revealed an *N*-methyl aminoxy functionality suitable for neo-glycosylation. It could be functionalized with a complex oligosaccharide such as 6-sialyl lactose bearing a free reducing end under mild acidic conditions. A successful glycosylation and the degree of functionalization was confirmed by NMR and diffusion coefficients of both the glycosylated and non-glycosylated polymer. The attraction of ligation of reducing glycans with *N*-methyl aminoxy containing compounds is that the pyranosyl structure is maintained without introducing unnatural linkers. The NCA polymerization allows for functionalization of a large range of complex oligosaccharides having a reducing end, to give neoglycopolymers for various applications. Such sacchar-



ides can be obtained from natural sources or through chemical- or chemoenzymatic synthesis.<sup>44,45</sup> The use of complex oligosaccharides is of particular interest because such compounds are expected to bind much more selectively to glycan binding proteins. The resulting highly glycosylated polymers can mimic mucins<sup>46</sup> that may find multiple application for example as antiviral agent.

## Experimental

### *tert*-Butyl hydroxy(methyl)carbamate (2)

*tert*-Butyl hydroxy(methyl)carbamate (2) was made according to a literary procedure.<sup>36</sup> *N*-Methyl hydroxylamine hydrochloride (16.72 g, 0.2 mol) was dissolved in = THF/H<sub>2</sub>O (80 mL, 1/1, v/v). The mixture was cooled in an ice bath and K<sub>2</sub>CO<sub>3</sub> (16.7 g, 0.12 mol) was added. Di-*tert*-butyl dicarbonate (48.3 g, 0.22 mol) was dissolved in THF (60 mL) and added dropwise to the mixture over a period of 45 min. The resulting reaction mixture was stirred for 1.5 h at 0 °C and then for 1.5 h at room temperature. The reaction mixture was concentrated *in vacuo* and the residue redissolved in DCM (100 mL) and then washed with NaHCO<sub>3</sub> (40 mL), twice with H<sub>2</sub>O (40 mL) and once with brine (50 mL). The organic layer was dried (MgSO<sub>4</sub>), filtered and the filtrate concentrated *in vacuo*. The residue was purified by silica gel column chromatography using a gradient of pure toluene to 10% EtOAc in toluene to yield *tert*-butyl hydroxy(methyl)carbamate 2 as a clear oil (17.6 g, 0.12 mol, 60%). <sup>1</sup>H NMR (400 MHz, Chloroform-*d*): δ 6.56 (1H, br s, OH), 3.14 (3H, s, N-CH<sub>3</sub>), 1.47 (9H, s, CH<sub>3</sub>, Boc). <sup>13</sup>C NMR (100 MHz, Chloroform-*d*) δ 157.7 (C=O Boc), 82.1 (CMe<sub>3</sub> Boc), 37.8 (NMe), 28.4 (3 × CH<sub>3</sub>, Boc).<sup>47</sup> ESI-TOF: *m/z* calculated for C<sub>6</sub>H<sub>14</sub>NO<sub>3</sub><sup>+</sup> (M + H) 148.090, found 148.092.

### Methyl *O*-((*tert*-butoxycarbonyl)(methyl)amino)-*N*-trityl-L-serinate (3)

*N*-Trityl-L-serine methyl ester (10.02 g, 27.7 mmol), *tert*-butyl hydroxy(methyl)carbamate 2 (5.01 g, 34.0 mmol) and triphenylphosphine (8.68 g, 33.1 mmol) were dissolved in toluene (60 mL) and the resulting solution was placed under an atmosphere of N<sub>2</sub>. The mixture was cooled in an ice bath and diisopropyl-azodicarboxylate (DIAD, 7.0 mL, 33.5 mmol) was added dropwise. The reaction mixture was heated under reflux for 2 h. Next, the reaction mixture was concentrated *in vacuo* and the residue redissolved in DCM (150 mL). The organic layer was washed twice with H<sub>2</sub>O (150 mL) and once with brine (200 mL). The organic layer was dried (MgSO<sub>4</sub>), filtered and the filtrate was concentrated *in vacuo*. The residue was purified by silica gel column chromatography using a gradient from 1% EtOAc in PE to 10% EtOAc in PE to give methyl *O*-((*tert*-butoxycarbonyl)(methyl)amino)-*N*-trityl-L-serinate (Tr-Ser(N(Me)Boc)-OMe) 3 (5.32 g, 10.8 mmol, 39% as a clear oil). <sup>1</sup>H NMR (600 MHz, Chloroform-*d*) δ 7.50 (d, *J* = 7.3 Hz, 6H, Tr), 7.25 (t, *J* = 7.7 Hz, 6H, Tr), 7.18 (t, *J* = 7.3 Hz, 3H, Tr), 4.18 (dd, *J* = 9.4, 4.3 Hz, 1H, β-CH<sub>2</sub>), 3.85 (dd, *J* = 9.4, 6.7 Hz, 1H, β-CH<sub>2</sub>), 3.54 (ddd, *J* = 10.7, 6.7, 4.3 Hz, 1H, α-CH), 3.24 (s, 3H,

*O*-CH<sub>3</sub>), 3.03 (s, 3H, N-CH<sub>3</sub>), 1.48 (s, 9H, CH<sub>3</sub>, Boc). <sup>13</sup>C NMR (151 MHz, Chloroform-*d*) δ 173.60 (C=O, Boc), 145.75 (C=O, CO<sub>2</sub>Me), 128.78 (Tr, Ar), 127.90 (Tr, Ar), 126.53 (Tr, Ar), 81.42 (C, Boc), 71.10 (C, Tr), 55.56 (β-CH<sub>2</sub>), 51.86 (α-CH), 36.66 (CH<sub>3</sub>, C-O), 30.95 (CH<sub>3</sub>, C-N), 28.30 (CH<sub>3</sub>, Boc). ESI-TOF: *m/z* calculated for C<sub>29</sub>H<sub>35</sub>N<sub>2</sub>O<sub>5</sub><sup>+</sup> (M + H) 491.247, found 491.245.

### *O*-((*tert*-Butoxycarbonyl)(methyl)amino)-L-serine (4)

Methyl *O*-((*tert*-butoxycarbonyl)(methyl)amino)-*N*-trityl-L-serinate 3 (5.32 g, 10.84 mmol) was dissolved in DCM (40 mL) and several drops of MeOH were added. The mixture was placed in an ice bath and TFA (0.8 mL) was added dropwise. After stirring the reaction mixture for 2 h, another portion of TFA (0.4 mL) was added dropwise and after another 2.5 h another portion of TFA (0.4 mL) was added dropwise. After 5 h, the reaction was quenched with saturated aqueous NaHCO<sub>3</sub> (40 mL) and the aqueous layer was washed three times with DCM (50 mL). The combined organic layers were dried (MgSO<sub>4</sub>), filtered and filtrate concentrated *in vacuo*. Without further purification, the crude product (2.13 g, 8.58 mmol) was dissolved in THF (60 mL) and a solution of H<sub>2</sub>O (21 mL) and 1 M aqueous NaOH (9 mL) was added dropwise on ice over the course of half an hour. Acetic acid was added until a neutral pH was reached, and the mixture was concentrated *in vacuo*. The residue was purified using reverse phase C<sub>18</sub> chromatography using a mixture of 5% MeCN in H<sub>2</sub>O. Fractions were checked by MS and those containing the product were combined and lyophilized to yielded *O*-((*tert*-butoxycarbonyl)(methyl)amino)-L-serine 4 (1.46, 73%) as a white amorphous solid. <sup>1</sup>H NMR (400 MHz, deuterium oxide) δ 4.34–4.28 (m, 2H, β-CH<sub>2</sub>), 4.04–3.98 (m, 1H), α-CH<sub>2</sub>, 3.16 (d, *J* = 1.2 Hz, 3H, N-CH<sub>3</sub>), 1.51 (s, 9H, Boc). <sup>13</sup>C NMR (101 MHz, deuterium oxide) δ 170.89 (C=O, Boc), 158.16 (C=O, CO<sub>2</sub>H), 84.21 (C, Boc), 71.46 (β-CH<sub>2</sub>), 53.41 (α-CH), 35.68 (N-CH<sub>3</sub>), 27.36 (CH<sub>3</sub>, Boc). ESI-TOF: *m/z* calculated for C<sub>9</sub>H<sub>19</sub>N<sub>2</sub>O<sub>5</sub><sup>+</sup> (M + H) 235.122, found 235.129.

### *N*-Carboxyanhydride *O*-((*tert*-butoxycarbonyl)(methyl)amino)-L-serine (1)

*O*-((*tert*-Butoxycarbonyl)(methyl)amino)-L-serine 4 (100.8 mg, 0.43 mmol) was dissolved in THF (15 mL) and propylene oxide (0.2 mL, 2.85 mmol) was added followed by triphosgene (83 mg, 0.28 mmol). The reaction mixture was stirred at room temperature for 1.5 h. The reaction mixture was cooled in an ice bath (3 mi.) and then quenched with water (15 mL). The aqueous layer was washed with EtOAc (2 × 40 mL) and the combined organic layers were washed with brine (80 mL). The organic layer was dried (MgSO<sub>4</sub>), filtered and the filtrate concentrated *in vacuo*. The residue was purified using anhydrous flash silica gel column chromatography (dry solvents, oven-dried silica gel and under N<sub>2</sub> stream)<sup>27</sup> using PE/EtOAc (1/1, v/v) to yield *N*-carboxyanhydride *O*-((*tert*-butoxycarbonyl)(methyl)amino)-L-serine 1 (77.0 mg, 0.29 mmol, 69%) as a white amorphous solid. <sup>1</sup>H NMR (400 MHz, Chloroform-*d*) δ 4.58 (dd, *J* = 10.0, 3.1 Hz, 1H, β-CH<sub>2</sub>), 4.22 (dd, *J* = 11.8, 3.4 Hz, 1H, β-CH<sub>2</sub>), 3.90 (dd, *J* = 11.8, 9.9 Hz, 1H, α-CH<sub>2</sub>), 3.08 (s, 3H, N-CH<sub>3</sub>), 1.47 (s, 9H, Boc). <sup>13</sup>C NMR (101 MHz, Chloroform-*d*) δ 176.89, 164.16, 146.10, 90.21, 77.46, 59.41, 41.68, 33.36.



ESI-TOF:  $m/z$  calculated for  $C_{10}H_{17}N_2O_6^+$  ( $M + H$ ) 261.108, found 261.110.

#### Poly-*O*-((*tert*-butoxycarbonyl)(methylamino)-*L*-serine (5)

*N*-Carboxyanhydride *O*-((*tert*-butoxycarbonyl)(methylamino)-*L*-serine **1** (65 mg, 0.25 mmol) was dissolved in DCM (2.3 mL). Lithium-bis-(trimethylsilyl)-amid (0.1 mL, 1 M in THF) was diluted in anhydrous DCM (1.9 mL, 50 mM). From the resulting solution 0.1 mL (5  $\mu$ mol 1 : 50 *I/M*) were added at once to the reaction vessel and the reaction was left stirring for 1.5 h at room temperature. The reaction mixture was then poured into cold PE/Et<sub>2</sub>O (1 : 1, 10 mL). The mixture was centrifuged at 4500 rpm for 5 min, the supernatant was removed and the pellet was washed with PE (30 mL, 3 $\times$ ) to yield poly-*O*-((*tert*-butoxycarbonyl)(methylamino)-*L*-serine **5** (50 mg, 93%, 0.003 mmol) as a white powder. <sup>1</sup>H NMR (400 MHz, Chloroform-*d*)  $\delta$  4.65 (bs, 1H,  $\alpha$ -CH), 4.17 (bs, 1H,  $\beta$ -CH<sub>2</sub>), 4.00 (bs, 1H,  $\beta$ -CH<sub>2</sub>), 3.08 (bs, 3H, N-CH<sub>3</sub>), 1.44 (bs, 9H, Boc). <sup>1</sup>H-<sup>13</sup>C NMR (400, 101 MHz, Chloroform-*d*)  $\delta$  (4.65, 52.36), (4.17, 73.21), (4.03, 73.21), (3.06, 37.15), (1.44, 28.32). The <sup>13</sup>C signals were obtained from an HSQC experiment.

#### Poly-*O*-(methylamino)-*L*-serine (6)

Poly-*O*-((*tert*-butoxycarbonyl)(methylamino)-*L*-serine **5** (5.7 mg, 0.4  $\mu$ mol) was dissolved in TFA/H<sub>2</sub>O (1.5 mL, 1/1, v/v). The reaction mixture was left stirring at room temperature for 4.5 hours. The reaction mixture was then diluted with H<sub>2</sub>O until the TFA concentration was 10% (v/v) and then lyophilized. The residue was purified by size exclusion column chromatography using extra fine polyacrylamide beads (P2 Bio-gel) and ammonium bicarbonate buffer (20 mM) as the eluent to yield poly-*O*-(methylamino)-*L*-serine **6** as a white powder (1.6 mg, 0.21  $\mu$ mol, 52%). <sup>1</sup>H NMR (600 MHz, deuterium oxide)  $\delta$  4.69 (bs, 1H,  $\alpha$ -CH), 4.04 (bs, 2H,  $\beta$ -CH<sub>2</sub>), 2.65 (bs, 3H, N-Me). <sup>1</sup>H-<sup>13</sup>C NMR (600, 151 MHz, deuterium oxide)  $\delta$  (4.69, 53.20), (4.04, 71.29), (2.65, 37.67). The <sup>13</sup>C signals were obtained from an HSQC experiment.

#### $\alpha$ 2,6-Sialyllactose (7)

$\alpha$ 2,6-Sialyllactose (**7**) was prepared enzymatically according to a reported procedure.<sup>40</sup> *D*-Lactose monohydrate (20.2 mg, 0.056 mmol) and CMP-Neu5Ac (70.8 mg, 0.11 mmol) were dissolved in Tris-HCl (pH 8.5, 1 M, 100  $\mu$ L), MilliQ (780  $\mu$ L) and aqueous MgCl<sub>2</sub> (0.2 M, 100  $\mu$ L). PmST1 (P34H/M144L) (20  $\mu$ L, 1 mg mL<sup>-1</sup> Tris HCl solution (100 mM pH 7.4)) was added, and the reaction mixture was incubated at 37 °C for 2.5 h. The reaction was incubated at 37 °C for 65 h. The reaction mixture was loaded on a P-2 Bio-gel column which was eluted with 0.1 M NH<sub>4</sub>HCO<sub>3</sub> to yield  $\alpha$ 2,6-sialyl lactose **7** after combining and lyophilizing product containing fractions (33.1 mg, 94%) as a white powder. <sup>1</sup>H NMR (600 MHz, deuterium oxide)  $\delta$  5.15 (0.41H, d,  $J$  = 3.8 Hz,  $\alpha$  anomer Glu), 4.59 (0.68H, d,  $J$  = 8.0 Hz,  $\beta$  anomer Glu), 4.35 (1H, d,  $J$  = 7.9 Hz, C<sub>1</sub>H Gal), 3.93–3.69 (10H, m), 3.65 (1H, dd), 3.61–3.37 (8H, m), 3.23 (0.63H, t, C<sub>2</sub>H  $\beta$  Glu), 2.64 (1H, dd, H3"), 1.95 (3H, s, acetyl), 1.67 (1H, t,  $J$  = 12.2 Hz, C<sub>3</sub>H<sub>2</sub> Sia). <sup>1</sup>H-<sup>13</sup>C NMR: (600, 151 MHz, deuterium

oxide)  $\delta$ 108.20 (C<sub>1</sub> Gal), 95.63 (C<sub>1</sub>  $\alpha$  anomer Glu), 91.84 (C<sub>1</sub>  $\beta$  anomer Glu), 76.67, 74.60, 73.68, 72.50, 72.34, 71.78, 71.62, 71.21, 70.77, 70.65, 70.41, 69.92, 69.76, 68.36, 63.65, 62.61, 60.25, 60.09, 51.76, 40.08 (C<sub>3</sub> Sia), 22.03 (CH<sub>3</sub>, acetyl). See for full assignment the Table S1 in the SI.<sup>40</sup> The <sup>13</sup>C signals were obtained from an HSQC experiment. ESI-TOF:  $m/z$  calculated for C<sub>23</sub>H<sub>40</sub>NO<sub>19</sub><sup>+</sup> ( $M + H$ ) 634.218, found 634.221.

#### Poly-*O*-(methylamino)-*L*-serine modified with $\alpha$ 2,6-sialyllactose (8)

Poly-*O*-(methylamino)-*L*-serine **6** (1.0 mg, 0.13  $\mu$ mol) and  $\alpha$ 2,6-sialyl lactose **7** (5.5 mg, 8.68  $\mu$ mol) were dissolved in a mixture of AcOH/DMF/H<sub>2</sub>O 2/1/1 (v/v). After stirring the reaction mixture for 24 h, the solvents were evaporated, and the residue was redissolved in MilliQ (7.5 mL) and then lyophilized. The crude material was purified by size exclusion gel chromatography (Bio-Gel P6 DG) using NH<sub>4</sub>HCO<sub>3</sub> (50 mM pH = 7.4) as the eluent yielding polymer **8** (3 mg, 82%). <sup>1</sup>H NMR (600 MHz, deuterium oxide)  $\delta$  4.37 (s, 1H), 3.96–3.70 (m, 9H), 3.68–3.39 (m, 12H), 2.64 (s, 5H) 2.57 (s, 2H), 1.96 (s, 3H), 1.72–1.63 (t,  $J_1$  = 12 Hz  $J_2$  = 24 Hz 1H). <sup>1</sup>H-<sup>13</sup>C NMR (600, 151 MHz, deuterium oxide)  $\delta$  (4.37, 103.35), (3.91, 63.57), (3.87, 68.60), (3.83, 71.92), (3.82, 62.73), (3.79, 51.95), (3.75, 73.77), (3.65, 72.53), (3.62, 76.37), (3.60, 72.53), (3.59, 68.60), (3.58, 62.86), (3.55, 79.76), (3.50, 68.60), (3.49, 76.37), (3.48, 70.89), (2.66, 38.06), (1.96, 22.16), (1.69, 40.25). The <sup>13</sup>C signals were obtained from an HSQC experiment.

## Author contributions

FP and GJB designed the study. FP, MW, and ER performed chemical synthesis. FP performed characterization of the polymers. JMD performed the DOSY NMR experiments. TV supervised the characterization of the polymers. GJB supervised all other aspects of the study. FP, TV, and GJB wrote the paper. All authors reviewed the manuscript.

## Conflicts of interest

The authors declare no conflict of interest.

## Data availability

The data underlying this study are available in the article and its SI. Supplementary information: general materials and methods, copies of <sup>1</sup>H, <sup>13</sup>C and 2D NMR spectra, Table S1, Fig. S1 and HR-MS data for synthetic compounds. See DOI: <https://doi.org/10.1039/d5ob00985e>.

## Acknowledgements

This work was supported by the EC H2020 Marie Curie doctorate COFUND RESCUE programme 'Regenerating Medicine Training Network'.



## References

- S. H. Wibowo, A. Sulistio, E. H. Wong, A. Blencowe and G. G. Qiao, Polypeptide films via *N*-carboxyanhydride ring-opening polymerization (NCA-ROP): past, present and future, *Chem. Commun.*, 2014, **50**, 4971–4988.
- A. Rasines Mazo, S. Allison-Logan, F. Karimi, N. J. Chan, W. Qiu, W. Duan, N. M. O'Brien-Simpson and G. G. Qiao, Ring opening polymerization of alpha-amino acids: advances in synthesis, architecture and applications of polypeptides and their hybrids, *Chem. Soc. Rev.*, 2020, **49**, 4737–4834.
- R. E. Detwiler, A. E. Schlirf and J. R. Kramer, Rethinking transition metal catalyzed *N*-carboxyanhydride polymerization: Polymerization of Pro and AcOPro *N*-carboxyanhydrides, *J. Am. Chem. Soc.*, 2021, **143**, 11482–11489.
- Y. Wu, K. Chen, J. Wang, M. Chen, W. Dai and R. Liu, Recent advances and future developments in the preparation of polypeptides via *N*-carboxyanhydride (NCA) ring-opening polymerization, *J. Am. Chem. Soc.*, 2024, **146**, 24189–24208.
- C. Deng, J. T. Wu, R. Cheng, F. H. Meng, H. A. Klok and Z. Y. Zhong, Functional polypeptide and hybrid materials: Precision synthesis via  $\alpha$ -amino acid *N*-carboxyanhydride polymerization and emerging biomedical applications, *Prog. Polym. Sci.*, 2014, **39**, 330–364.
- D. Huesmann, K. Klinker and M. Barz, Orthogonally reactive amino acids and end groups in NCA polymerization, *Polym. Chem.*, 2017, **8**, 957–971.
- L. Li, J. Cen, W. Pan, Y. Zhang, X. Leng, Z. Tan, H. Yin and S. Liu, Synthesis of polypeptides with high-fidelity terminal functionalities under NCA monomer-starved conditions, *Research*, 2021, **2021**, 9826046.
- H. Lu and J. Cheng, *N*-trimethylsilyl amines for controlled ring-opening polymerization of amino acid *N*-carboxyanhydrides and facile end group functionalization of polypeptides, *J. Am. Chem. Soc.*, 2008, **130**, 12562–12563.
- I. Conejos-Sánchez, A. Duro-Castano, A. Birke, M. Barz and M. J. Vicent, A controlled and versatile NCA polymerization method for the synthesis of polypeptides, *Polym. Chem.*, 2013, **4**, 3182–3186.
- J. Zou, J. Fan, X. He, S. Zhang, H. Wang and K. L. Wooley, A facile glovebox-free strategy to significantly accelerate the syntheses of well-defined polypeptides by *N*-carboxyanhydride (NCA) ring-opening polymerizations, *Macromolecules*, 2013, **46**, 4223–4226.
- Y. Nie, X. Zhi, H. Du and J. Yang, Zn(OAc)<sub>2</sub>-catalyzing ring-opening polymerization of *N*-carboxyanhydrides for the synthesis of well-defined polypeptides, *Molecules*, 2018, **23**, 760.
- Y. Wu, D. Zhang, P. Ma, R. Zhou, L. Hua and R. Liu, Lithium hexamethyldisilazide initiated superfast ring opening polymerization of alpha-amino acid *N*-carboxyanhydrides, *Nat. Commun.*, 2018, **9**, 5297.
- J. R. Kramer and T. J. Deming, Glycopolypeptides via living polymerization of glycosylated-L-lysine *N*-carboxyanhydrides, *J. Am. Chem. Soc.*, 2010, **132**, 15068–15071.
- J. R. Kramer, B. Onoa, C. Bustamante and C. R. Bertozzi, Chemically tunable mucin chimeras assembled on living cells, *Proc. Natl. Acad. Sci. U. S. A.*, 2015, **112**, 12574–12579.
- A. C. Deleray and J. R. Kramer, Biomimetic glycosylated polythreonines by *N*-carboxyanhydride polymerization, *Biomacromolecules*, 2022, **23**, 1453–1461.
- J. R. Kramer and T. J. Deming, Recent advances in glycopolypeptide synthesis, *Polym. Chem.*, 2014, **5**, 671–682.
- K. S. Krannig and H. Schlaad, Emerging bioinspired polymers: glycopolypeptides, *Soft Matter*, 2014, **10**, 4228–4235.
- M. N. Zhou, C. S. Delaveris, J. R. Kramer, J. A. Kenkel, E. G. Engleman and C. R. Bertozzi, *N*-carboxyanhydride polymerization of glycopolypeptides that activate antigen-presenting cells through dectin-1 and dectin-2, *Angew. Chem., Int. Ed.*, 2018, **57**, 3137–3142.
- C. S. Delaveris, E. R. Webster, S. M. Banik, S. G. Boxer and C. R. Bertozzi, Membrane-tethered mucin-like polypeptides sterically inhibit binding and slow fusion kinetics of influenza A virus, *Proc. Natl. Acad. Sci. U. S. A.*, 2020, **117**, 12643–12650.
- J. Huang, G. Habraken, F. Audouin and A. Heise, Hydrolytically stable bioactive synthetic glycopeptide homo- and copolymers by combination of NCA polymerization and click reaction, *Macromolecules*, 2010, **43**, 6050–6057.
- C. Xiao, C. Zhao, P. He, Z. Tang, X. Chen and X. Jing, Facile synthesis of glycopolypeptides by combination of ring-opening polymerization of an alkyne-substituted *N*-carboxyanhydride and click “glycosylation”, *Macromol. Rapid Commun.*, 2010, **31**, 991–997.
- K.-S. Krannig and H. Schlaad, in *Heterofunctional glycopolypeptides by combination of thiol-ene chemistry and NCA polymerization*, Ed. X. L. Sun, Humana Press, New York, 2016, vol. 1367, pp. 61–67.
- T. J. Deming, Synthesis of side-chain modified polypeptides, *Chem. Rev.*, 2016, **116**, 786–808.
- C. Lavilla, G. Yilmaz, V. Uzunova, R. Napier, C. R. Becer and A. Heise, Block-sequence-specific glycopolypeptides with selective lectin binding properties, *Biomacromolecules*, 2017, **18**, 1928–1936.
- V. Dhaware, D. Díaz Díaz and S. Sen Gupta, Biopolymer/glycopolypeptide-blended scaffolds: Synthesis, characterization and cellular interactions, *Chem. – Asian J.*, 2019, **14**, 4837–4846.
- S. M. Banik, K. Pedram, S. Wisnovsky, G. Ahn, N. M. Riley and C. R. Bertozzi, Lysosome-targeting chimaeras for degradation of extracellular proteins, *Nature*, 2020, **584**, 291–297.
- L. Zhao, C. Xiao, J. Ding, X. Zhuang, G. Gai, L. Wang and X. Chen, Competitive binding-accelerated insulin release from a polypeptide nanogel for potential therapy of diabetes, *Polym. Chem.*, 2015, **6**, 3807–3815.
- S. Ulrich, D. Boturyn, A. Marra, O. Renaudet and P. Dumy, Oxime ligation: a chemoselective click-type reaction for



- accessing multifunctional biomolecular constructs, *Chem. – Eur. J.*, 2014, **20**, 34–41.
- 29 F. Peri, P. Dumy and M. Mutter, Chemo- and stereoselective glycosylation of hydroxylamino derivatives: A versatile approach to glycoconjugates, *Tetrahedron*, 1998, **54**, 12269–12278.
- 30 M. R. Carrasco, M. J. Nguyen, D. R. Burnell, M. D. MacLaren and S. M. Hengel, Synthesis of neoglycopeptides by chemoselective reaction of carbohydrates with peptides containing a novel *N*'-methyl-aminooxy amino acid, *Tetrahedron Lett.*, 2002, **43**, 5727–5729.
- 31 M. R. Carrasco, O. Silva, K. A. Rawls, M. S. Sweeney and A. A. Lombardo, Chemoselective alkylation of *N*-alkylaminooxy-containing peptides, *Org. Lett.*, 2006, **8**, 3529–3532.
- 32 P. B. Konietzny, J. Freytag, M. I. Feldhof, J. C. Müller, D. Ohl, T. Stehle and L. Hartmann, Synthesis of homo- and heteromultivalent fucosylated and sialylated oligosaccharide conjugates *via* preactivated *N*-methoxyamine precision macromolecules and their binding to polyomavirus capsid proteins, *Biomacromolecules*, 2022, **23**, 5273–5284.
- 33 A. L. Wollenberg, P. Perlin and T. J. Deming, Versatile *N*-methylaminooxy-functionalized polypeptides for preparation of neoglycoconjugates, *Biomacromolecules*, 2019, **20**, 1756–1764.
- 34 E. C. Rodriguez, L. A. Marcaurelle and C. R. Bertozzi, Aminooxy-, hydrazide-, and thiosemicarbazide-functionalized saccharides: Versatile reagents for glycoconjugate synthesis, *J. Org. Chem.*, 1998, **63**, 7134–7135.
- 35 R. D. Goff and J. S. Thorson, Neoglycosylation and neoglycorandomization: Enabling tools for the discovery of novel glycosylated bioactive probes and early stage leads, *MedChemComm*, 2014, **5**, 1036–1047.
- 36 M. R. Carrasco, R. T. Brown, I. M. Serafimova and O. Silva, Synthesis of *N*-Fmoc-O- (*N*'-Boc-*N*'-methyl)-aminohomoserine, an amino acid for the facile preparation of neoglycopeptides, *J. Org. Chem.*, 2003, **68**, 195–197.
- 37 Z. Y. Tian, Z. Zhang, S. Wang and H. Lu, A moisture-tolerant route to unprotected alpha/beta-amino acid *N*-carboxyanhydrides and facile synthesis of hyperbranched polypeptides, *Nat. Commun.*, 2021, **12**, 5810.
- 38 J. R. Kramer and T. J. Deming, General method for purification of alpha-amino acid-*N*-carboxyanhydrides using flash chromatography, *Biomacromolecules*, 2010, **11**, 3668–3672.
- 39 G. J. M. Habraken, K. H. R. M. Wilsens, C. E. Koning and A. Heise, Optimization of *N*-carboxyanhydride (NCA) polymerization by variation of reaction temperature and pressure, *Polym. Chem.*, 2011, **2**, 1322–1330.
- 40 J. B. McArthur, H. Yu, J. Zeng and X. Chen, Converting *Pasteurella multocida* alpha2–3-sialyltransferase 1 (PmST1) to a regioselective alpha2–6-sialyltransferase by saturation mutagenesis and regioselective screening, *Org. Biomol. Chem.*, 2017, **15**, 1700–1709.
- 41 S. Viel, D. Capitani, L. Mannina and A. Segre, Diffusion-ordered NMR spectroscopy: a versatile tool for the molecular weight determination of uncharged polysaccharides, *Biomacromolecules*, 2003, **4**, 1843–1847.
- 42 P. Groves, Diffusion ordered spectroscopy (DOSY) as applied to polymers, *Polym. Chem.*, 2017, **8**, 6700–6708.
- 43 J. Kalia and R. T. Raines, Hydrolytic stability of hydrazones and oximes, *Angew. Chem., Int. Ed.*, 2008, **47**, 7523–7526.
- 44 L. Liu, A. R. Prudden, G. P. Bosman and G. J. Boons, Improved isolation and characterization procedure of sialylglycopeptide from egg yolk powder, *Carbohydr. Res.*, 2017, **452**, 122–128.
- 45 L. Liu, A. R. Prudden, C. J. Capicciotti, G. P. Bosman, J. Y. Yang, D. G. Chapla, K. W. Moremen and G. J. Boons, Streamlining the chemoenzymatic synthesis of complex N-glycans by a stop and go strategy, *Nat. Chem.*, 2019, **11**, 161–169.
- 46 C. S. Kwan, A. R. Cerullo and A. B. Braunschweig, Design and synthesis of mucin-inspired glycopolymers, *ChemPlusChem*, 2020, **85**, 2704–2721.
- 47 M. J. S. Smith, W. Tu, C. M. Robertson and J. F. Bower, Stereospecific aminative cyclizations triggered by intermolecular aza-prilezhaev alkene aziridination, *Angew. Chem., Int. Ed.*, 2023, **62**, e202312797.

