RSC Advances



REVIEW

View Article Online
View Journal | View Issue



Cite this: RSC Adv., 2025, 15, 4789

efficiency dye-sensitized solar cells Kumar Vaisno Srivastava ^a Pooia Srivastava ^b Akancha Srivastava ^b Rai Kumar Maur

1D TiO₂ photoanodes: a game-changer for high-

Hierarchical architectures encompassing one-dimensional (1D), two-dimensional (2D), and threedimensional (3D) nanostructures have garnered significant attention in energy and environmental applications due to their unique structural, electronic, and optical properties. These architectures provide high surface area, enhanced charge transport pathways, and improved light-harvesting capabilities, making them versatile candidates for next-generation photovoltaic (PV) systems. Among these, 1D structures, such as nanorods, nanowires, and nanotubes, offer distinct advantages, including anisotropic charge transport, reduced recombination rates, and enhanced light absorption due to their high aspect ratio and directional charge flow. In this focused review article, the pivotal role of one-dimensional titanium dioxide (1-D TiO₂) as photoanodes in dye-sensitized solar cells (DSSCs) has been discussed thoroughly. The distinctive morphology of 1-D TiO2, including nanotubes or nanorods, provides an expanded surface area, facilitating efficient light absorption and dye adsorption. The inherent onedimensional architecture promotes accelerated electron transport, minimizing recombination losses and enhancing charge collection efficiency. Additionally, 1-D TiO₂ structures exhibit superior charge carrier mobility, reducing trapping sites and enhancing electron diffusion pathways, thereby improving overall stability and performance. The scalability and cost-effectiveness of synthesizing 1-D TiO2 nanostructures underscore their potential for large-scale DSSC production. This research emphasizes the significance of 1-D TiO₂ as a promising photoanode material, offering a pathway for advancing the efficiency and viability of dye-sensitized solar cell applications.

Received 29th August 2024 Accepted 27th December 2024

DOI: 10.1039/d4ra06254i

rsc.li/rsc-advances

1. Introduction

The excessive use of fossil fuels to meet our growing energy needs has resulted in significant consequences such as global warming and environmental pollution. To address these challenges and achieve a sustainable energy future, it is crucial to adopt an energy production approach that relies on renewable sources. While options like geothermal energy, biofuels, and wind-tidal energies can contribute to sustainable development, solar energy stands out as a particularly important solution. In this era of increasing energy demands and environmental concerns, solar radiation offers immense potential, abundant availability, and environmental friendliness.1 Out of the 4 million exajoules (1018 J) of solar energy reaching the Earth, approximately 50 000 EJ can be easily harnessed. The significance of solar energy is underscored by the fact that the world's annual energy consumption in 2017 amounted to approximately 565 exajoules (EJ), which represents a mere fraction of the potential solar energy harvest of around 50 000 EJ. However, the current contribution of the renewable energy sector to

global electricity production stands at a modest 8.4%. Notably, solar energy accounts for over 20% of this renewable energy share.² Despite this, the utilization of solar energy remains disproportionately small compared to the vast solar power available for exploitation. The primary reason for this disparity lies in the absence of efficient and economically viable solar harvesting techniques. Among the diverse solar energy conversion devices, first-generation silicon solar cells have gained prominence as the most extensively commercialized type.

Silicon solar cells have achieved efficiencies of approximately 26%, approaching the theoretical maximum efficiency. In contrast, second-generation solar cells utilize thin-film technology and employ materials like CdTe and CIGS, reaching efficiencies of up to 21.7% in recent developments. However, the widespread commercialization of first and second-generation solar cells remains costly, and the materials used in these generations can pose environmental hazards. To address these challenges and create an economically viable and environmentally friendly approach to solar energy conversion, the concept of dye-sensitized solar cells (DSSCs) was introduced as the third generation of solar cells. DSSCs, first proposed by Michael Grätzel in 1991, have garnered significant attention due to their potential for large-scale, cost-effective production and

^aDepartment of Physics, Mangalayatan University, Aligarh 202146, India ^aDepartment of Physics, Dr RML Avadh University, Ayodhya 224001, India

flexibility.⁶ Currently, the efficiencies of DSSCs are within the range of 14.3%.⁷ DSSCs have the potential to play a crucial role in advancing sustainable energy culture if the challenges of low efficiency and limited durability are effectively addressed.

The large-scale commercialization of DSSCs can harness a significant portion of the available solar radiation. Enhancing performance, improving durability, and reducing production costs of DSSCs can be achieved through various approaches. This involves synthesizing novel component materials or modifying existing materials and introducing more optimized DSSC designs.8 As DSSC assemblies consist of multiple components such as the photoanode, sensitizer (dye), counter electrode, and redox electrolyte, efforts to enhance performance can be focused on any of these components.9 This review specifically highlights the significance of 1-D TiO₂ nanorodsbased photoanodes for the critical advancement of DSSCs. Specifically, 1D nanorods were selected due to their superior directional charge transport, enhanced light scattering properties, and higher surface area-to-volume ratio, which collectively improve photocatalytic and photoelectrochemical performance. Despite their high surface area, nanoparticles suffer from significant interparticle recombination and poor charge transport due to grain boundaries, limiting their overall efficiency.10 Nanowires and nanofibers, while offering continuous 1-D pathways for charge transport, have lower surface areas, which can restrict dye loading and limit their light-harvesting capability. In contrast, nanorods strike an optimal balance between surface area and charge transport. Their unidirectional structure facilitates efficient electron transport with reduced recombination compared to nanoparticles, while their higher surface area relative to nanowires enables improved dye loading and light absorption.11 Additionally, the tunable aspect ratio of nanorods allows for enhanced light scattering and extended photon absorption paths, making them highly effective as photoanodes. This provides a robust background for the study and highlights the rationale behind using nanorods as the preferred architecture for DSSC applications.12

Additionally, heterojunction solar cells, compared to DSSCs, have many demerits. Thin-film solar cells suffer from higher charge recombination rates due to the presence of multiple interfaces, which act as recombination centers, thereby reducing charge carrier lifetime and overall efficiency. Additionally, their thin active layers, typically less than a few hundred nanometres, limit light absorption, particularly in the red and near-infrared regions of the solar spectrum, resulting in suboptimal photon utilization. 13,14 These devices also exhibit thermal and mechanical instability, with a higher tendency for delamination, cracking, and degradation under prolonged thermal or mechanical stress, which negatively impacts their long-term operational stability. Moreover, the fabrication of thin-film solar cells is complex, often requiring vacuum deposition, high-temperature processing, and precise control over layer thickness and composition, leading to higher production costs and limited scalability. 15,16 In contrast, DSSCs offer several advantages, including simpler, solution-based fabrication methods, lower sensitivity to defects, and better performance under low-light and diffuse lighting conditions.

Therefore, this review explores the advancements and potential of 1-D TiO₂ nanorods as a most promising photoanodes in DSSCs. Their superior light-scattering properties, efficient electron transport, and well-matched band alignment with sensitizers make them promising candidates for high-performance DSSCs. Additionally, 1-D TiO₂ is favoured for its non-toxic nature and robust functionality in sustainable energy applications. Future research could focus on extending their light absorption into the infrared region and integrating them with advanced materials like perovskites, quantum dots, and MXenes to enhance energy capture, transfer, and storage. Addressing challenges related to scalability, surface engineering, and hybridisation could further position 1-D TiO₂-based DSSCs as pivotal in driving the global transition to clean and sustainable energy solutions.

2. Fundamentals of DSSC

2.1 Architecture

DSSCs are composed of several essential components that work together to convert sunlight into electricity, as shown in Fig. 1(a). The architecture begins with a transparent conductive substrate, typically made of fluorine-doped tin oxide (FTO) or indium tin oxide (ITO) on glass, which serves as the bottom electrode and allows light transmission. The photoanode, a thin layer of nanostructured TiO2 particles coated on the substrate, provides a large surface area for dye adsorption and facilitates electron transport. A light-absorbing sensitizer, such as ruthenium-based or organic dyes, is adsorbed onto the TiO2 surface to capture photons and inject excited electrons into the TiO2, initiating charge separation. A liquid electrolyte containing a redox couple (usually iodide/triiodide) facilitates charge transport by shuttling electrons between the photoanode and the counter electrode. The counter electrode, commonly made of platinum or carbonbased materials, catalyzes the reduction of the oxidized redox species and acts as the cathode. A transparent conductive layer on the counter electrode, often FTO or ITO, ensures efficient electron collection to complete the circuit. A sealing material such as glass or polymer is used for encapsulation to protect the cell from environmental factors. 18,19 When sunlight strikes the cell, the dye absorbs photons, resulting in electron excitation and injection into the TiO2. These electrons flow through the external circuit to the counter electrode, reducing the redox couple in the electrolyte and completing the electrical cycle. The unique architecture of DSSCs enables efficient light absorption, charge separation, and electron collection, making them a promising technology for solar energy conversion. Ongoing research aims to refine the architecture, explore novel materials, and improve both the efficiency and stability of these cells.20,21

2.2 Working principal

The working principle of DSSCs involves several key processes enabling sunlight-to-electricity conversion, as shown in Fig. 1(b). Upon illumination, the photoanode, composed of nanostructured ${\rm TiO_2}$ particles coated with dye molecules (sensitizers), absorbs light. Photons excite electrons in the dye to higher energy states, which are subsequently injected into the

Review RSC Advances

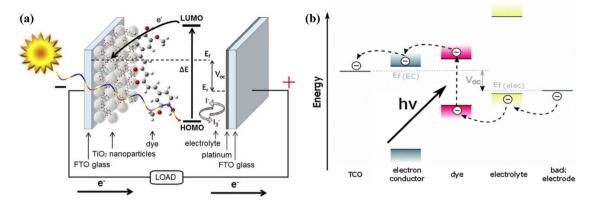


Fig. 1 (a) Schematic assembly of DSSC and typical working mechanism, 17 (b) typical band alignment of DSSC.

conduction band of TiO_2 due to favourable energy level alignment (eqn (1) and (2)). This creates charge separation, with electrons traveling through the TiO_2 network while oxidized dye molecules are regenerated via redox reactions in the electrolyte (eqn (3)). The electrolyte, containing an iodide/triiodide (I^-/I_3^-) redox couple, facilitates charge balance by reducing I_3^- to I^- at the photoanode and regenerating I_3^- at the counter electrode.

$$S + h\nu \to S^* \tag{1}$$

$$S^* \to S^+ + e^- (TiO_2) \tag{2}$$

$$2S^+ + 3I^- \rightarrow 2S + I_3^-$$
 (3)

$$I_3^- + 2e^- \rightarrow 3I^-$$
 (4)

Electrons injected into ${\rm TiO_2}$ travel through a conductive collecting layer to the counter electrode, typically platinum (Pt), where they catalyze the reduction of ${\rm I_3}^-$ to ${\rm I^-}$, completing the circuit and generating an electric current (eqn (4)). The continuous absorption of sunlight, charge separation, and electron transport ensure sustained electricity generation. DSSC efficiency is influenced by factors such as sensitizer properties, photoanode and counter-electrode design, and the effectiveness of light absorption and charge transport. Research is ongoing to optimize these components for improved performance and stability. $^{22-26}$

2.3 Electrical modelling and key parameters

Electrical modeling of DSSCs involves representing their behavior using an equivalent circuit that includes components mimicking the physical and chemical processes occurring within the cell. The key elements of the model include a photocurrent source ($I_{\rm ph}$), a diode (D), a series resistance ($R_{\rm Sl}$), and a shunt resistance ($R_{\rm Sh}$). The photocurrent source, $I_{\rm ph}$, represents the current generated by the photoanode due to light absorption and subsequent electron injection into the TiO₂ conduction band. It depends on factors like light intensity, dye absorption efficiency, and charge collection efficiency.

The diode models the recombination of photo-generated electrons with oxidized species in the electrolyte or the dye, with its current (I_D) described by the Shockley equation:

$$I_{\rm D} = I_0 \left(e^{\frac{q(V + IR_{\rm S})}{nKT}} - 1 \right) \tag{5}$$

where I_0 is the reverse saturation current, q is the elementary charge, n is the ideality factor, k is Boltzmann's constant, T is the temperature, V is the voltage across the cell, and R_S is the series resistance.

The $R_{\rm S}$ accounts for resistive losses in the TCO layer, the TiO₂ film, and the electrolyte. A lower $R_{\rm S}$ improves the fill factor and overall efficiency of the cell. The $R_{\rm Sh}$ represents leakage currents due to defects or imperfections in the device. A high $R_{\rm Sh}$ is desirable to minimize losses and improve device performance. The relationship between the total current (I) and voltage (V) in the DSSC is given by:

$$I = I_{\rm ph} - I_{\rm D} - \frac{V + IR_{\rm S}}{R_{\rm Sh}} \tag{6}$$

The power output of the cell can be derived as:

$$P = V \cdot I = V \cdot \left(I_{\text{ph}} - I_0 \left(e^{\frac{q(V + IR_S)}{nKT}} - 1 \right) - \frac{V + IR_S}{R_{\text{Sh}}} \right)$$
 (7)

Fig. 2 illustrates the current-voltage characteristics of a solar cell circuit under two conditions: in the dark and under illumination.27 In the absence of illumination, when the electrons traverse from the anode to the cathode or when the circuit is subjected to reverse bias, no current will flow due to the significant energy barrier presented by the donor material. Only after overcoming this energy barrier, a minimal current will be observed. This behaviour is depicted by the dark curve. Conversely, when the solar radiation is absorbed by the donor material, the generation of charge carriers becomes more facile. As a result, a reverse current occurs, where electrons flow from the anode to the cathode. This reverse current, in the absence of an external voltage, is referred to as the short circuit current density (I_{SC}) . This phenomenon is represented by the hollow bubbled curve. Key performance parameters include the opencircuit voltage $(V_{\rm OC})$, defined by the difference between the

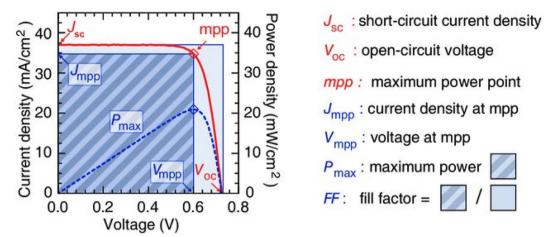


Fig. 2 Typical schematic representation of various J-V parameters to evaluate the solar cell performance.²⁷

quasi-Fermi level of electrons in TiO₂ and the redox potential of the electrolyte:

$$V_{\rm OC} = \frac{kT}{q} \ln \left(\frac{I_{\rm ph}}{I_0} + 1 \right) \tag{8}$$

By applying a forward voltage to the solar cell, it is feasible to counteract the short circuit current, effectively compensating for its flow. This compensation process continues until a specific voltage is reached, at which point the current diminishes to zero. This specific voltage is termed the $V_{\rm OC}$. On the other hand, the open circuit voltage represents the maximum attainable voltage across the terminals of a solar cell when it is not connected to an external load. In this state, no external current is drawn from the cell, and it operates under zero current conditions. The short-circuit current ($I_{\rm SC}$) is the maximum current delivered when V=0, and the fill factor (FF) is a measure of the shape of the current-voltage (I-V) curve, given by:

$$FF = \frac{P_{\text{max}}}{V_{\text{OC}} \cdot I_{\text{SC}}} \tag{9}$$

where P_{max} is the maximum power output. The power conversion efficiency (PCE) is then expressed as:

$$\eta = \frac{P_{\text{max}}}{P_{\text{in}}} = \frac{V_{\text{OC}} \cdot I_{\text{SC}} FF}{P_{\text{in}}}$$
 (10)

where $P_{\rm in}$ is the incident solar power.

This model facilitates a detailed understanding of DSSC performance and helps in optimizing parameters to enhance efficiency under varying operational conditions.

3. Importance of photoanodes in energy conversion

The photoanode plays a critical role in DSSCs by influencing photocurrent, photovoltage, and overall power conversion efficiency through its functions in dye absorption, electron injection, transport, and collection. Enhancing DSSC performance requires selecting suitable photoanode materials and optimizing their

morphologies. An ideal photoanode must possess a high surface area to enable extensive dye adsorption, thereby improving lightharvesting capabilities (Fig. 3(a and b)).28,31 Efficient electron transport is crucial for the rapid injection and transfer of electrons to the external circuit, ensuring effective utilization of absorbed photon energy. Proper band gap alignment between the photoanode and sensitizer facilitates optimal energy transfer, while high resistance to photo corrosion ensures stability and durability under prolonged light exposure (Fig. 3(c)).29,32 Additionally, optimizing pore size is essential for efficient dye and electrolyte diffusion, enabling improved mass transport within the cell.32 The photoanode material should also demonstrate strong sunlight absorption or scattering capabilities (Fig. 3(d)) to enhance light utilization and conversion efficiency.30 Furthermore, establishing effective contact between the photoanode, dye molecules, and conducting substrate is vital for ensuring efficient charge transfer and electron utilization.33 This review focuses on TiO₂ nanomaterials as photoanodes in DSSCs, highlighting their distinctive photovoltaic properties and key modifications to enhance performance. It provides a comprehensive overview of advancements in one-dimensional TiO2 morphologies and recent efforts to optimize their application as photoanode materials in DSSCs.

As shown in Fig. 3(a), Zhu et al.28 demonstrated the influence of TiO2 photoanode active surface area on charge transport and recombination. Fig. 3(a) shows a clear dependency of areal photoelectron density $(n_{oc}^{})$ on the V_{OC} . The $n_{oc}^{}$ is directly proportional to the film's roughness factor, as evidenced by similar values between 0.3 and 0.6 V for films with varying roughness factors, indicating that photoinjected electrons primarily reside on the particle surfaces under open-circuit conditions. At $V_{\rm OC} > 0.6$, a slight deviation from the exponential dependence occurs due to a band-edge shift caused by Helmholtz layer charging at the TiO₂ particle/electrolyte interface. 26,34 This results in a more rapid increase in $V_{\rm OC}$ with photoelectron density than predicted by exponential dependence. However, the normalized photoelectron density values remain consistent across samples with differing roughness factors.

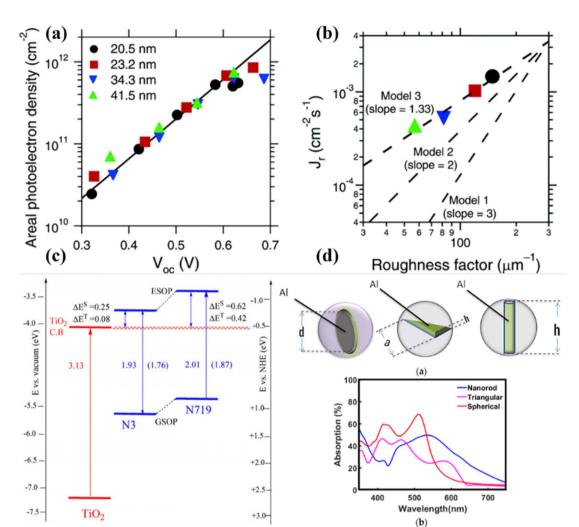


Fig. 3 Important features of photoanodes that can affect the DSSC performance significantly (a and b) photoanodes surface area and roughness-dependent photocurrent density, ²⁸ (c) suitable bandgap alignment for better charge injection and transfer, ²⁹ and (d) photoanode morphology-dependent tuning of light absorption capability, causing enhanced performance. ³⁰

In the same study, the recombination current density (J_r) as a function of the roughness factor (r_f) at $V_{\rm OC}=0.55$ V, with predictions based on three kinetic models. Model 1 predicts J_r $\propto (r_{\rm f})^3$, assuming a constant recombination rate (k_1) and twoelectron interfacial charge transfer. Model 2 predicts $J_r \propto (r_f)^2$, assuming J_r is first-order in photoelectron density and k_2 is constant at fixed V_{OC} . Model 3 predicts $J_r \propto (r_f)^{1,33}$ with J_r firstorder in photoelectron density and k_3 scaling with the electron diffusion coefficient, which depends on photoelectron density. The findings highlight that photoelectron density at an open circuit is proportional to the film roughness factor, with deviations at higher $V_{\rm OC}$ attributed to band-edge shifts. Additionally, recombination current density predictions from kinetic models emphasize the dependence on the roughness factor, reflecting varying assumptions about recombination processes and rate constants.

Further, Angelis *et al.* summarized the dye/ TiO_2 excited state energy levels in Fig. 3(c), and the excited state oxidation potential (ESOP) was calculated as the difference between the ground state oxidation potential (GSOP) and the lowest vertical

excitation energy (E_{0-0}) . The ESOP values align well with experimental data, especially when E_{0-0} is derived from $S_0 \rightarrow S_1$ transitions.²⁹ Also, the roughness factor directly influences the absorption coefficient and, simultaneously, the performance as well. As depicted in Fig. 3(d), the maximum absorption coefficient is observed in rod-like structures and is comparably high as compared to the disc and film-shaped photoanodes. Therefore, to design a photoanode for energy conversion, we must take care of proper band alignment, surface roughness, and structure for better light scattering and performance.

4. Typical photoanodes used in DSSC

Photoanode materials in DSSCs can be classified into several categories based on their composition and properties. Here are some common classifications of photoanode materials in DSSCs.

4.1 Metal oxides

Metal oxides are the most widely used class of photoanode materials in DSSCs. TiO₂ is the most common and extensively

studied metal oxide photoanode material due to its excellent stability, high electron mobility, and suitable band gap for efficient light absorption. Other metal oxides, such as SnO₂, ZnO, Fe₂O₃, Nb₂O₅, SrTiO₃, and Zn₂SnO₄, have also been explored as photoanode materials in DSSCs. The photoanode materials used in DSSCs are typically wide bandgap semiconductor materials. The performance of DSSCs is heavily influenced by the structural, morphological, and crystalline characteristics of these materials. The typical nanostructured morphology of these photoanode materials, which determines their electronic properties, can be observed in Fig. 4.35-38 The specific arrangement of atoms and the overall crystal structure significantly impact the light absorption, charge transport, and electron injection processes within the DSSC, ultimately influencing its overall performance.39,40

4.2 Nanomaterials

Nanomaterials such as nanoparticles, nanowires, nanotubes, and nanocomposites are widely employed as photoanodes in DSSCs due to their unique properties that enhance device performance. TiO₂ nanoparticles, for example, offer a high surface area for increased dye adsorption and light harvesting, but their charge transport is limited by interparticle boundaries. In contrast, 1-D structures like TiO₂ nanowires and ZnO nanorods provide direct electron transport pathways with reduced recombination, improving charge collection and

electron diffusion lengths. TiO2 nanotubes combine a high surface area with unidirectional charge transport, leading to improved charge separation and reduced recombination, resulting in higher PCE. Additionally, nanocomposites such as graphene-TiO2 and ZnO-TiO2 synergistically enhance electron mobility and light absorption, further boosting PCE. These examples demonstrate how nanomaterials optimize the performance of DSSC photoanodes through tailored structural and electronic properties. The revised text has been incorporated to reflect this discussion.41-43

Composite materials

Composite photoanode materials, integrating multiple components, have been extensively studied to harness the synergistic advantages of each constituent. For instance, composites of metal oxides (e.g., TiO2-ZnO) enhance charge transfer by combining the high electron mobility of ZnO with the superior dye adsorption and stability of TiO2. Similarly, incorporating carbon-based materials such as graphene improves electron transport and reduces recombination due to graphene's high conductivity and large surface area. Furthermore, the integration of organic semiconductors with metal oxides broadens light absorption into the visible range, enhancing photocurrent generation. These hybrid photoanodes improve overall device efficiency by simultaneously optimizing charge transport, light harvesting, and chemical stability,

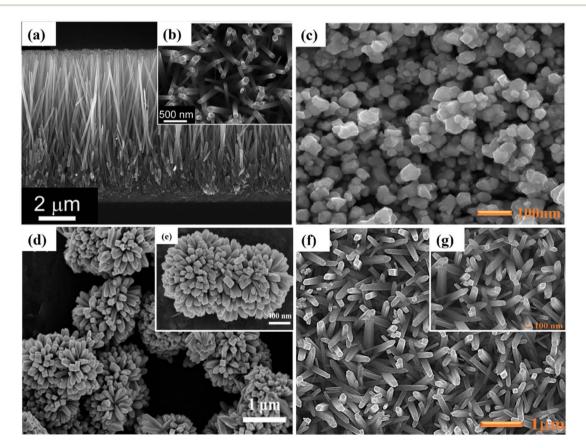


Fig. 4 Typical nanostructured FESEM images of various metal oxides that were generally used as a photoanode in DSSC applications. (a and b) ZnO-nanorods,³⁵ (c) Zn₂SnO₄-nanoparticles,³⁶ (d and e) SnO₂-nanoflower,³⁷ and (f and g) TiO₂-nanorods.³⁸

making them promising candidates for high-performance DSSCs.⁴⁴

5. Optoelectronic suitability of TiO_2 for DSSC application

The optoelectronic properties of TiO₂ play a pivotal role in the performance and efficiency of DSSCs. TiO2, particularly in its anatase phase, has emerged as the most widely used photoanode material due to its unique combination of physical and chemical characteristics. These include a suitable bandgap, high electron mobility, excellent chemical stability, and a large surface area that enables effective dye loading, making it wellsuited for light-harvesting applications in DSSCs. Firstly, the bandgap of anatase TiO2, approximately 3.2 eV, allows for efficient absorption of ultraviolet light, which constitutes a significant portion of the solar spectrum. Despite its wide bandgap limiting visible light absorption, various strategies, such as dye sensitization and bandgap tuning via doping, have been employed to enhance visible light capture. The intrinsic electronic structure of TiO₂ ensures that photo-excited electrons are injected into the semiconductor's conduction band with minimal energy losses, leading to efficient charge separation.45-47

Furthermore, TiO₂ exhibits favourable electron transport properties, with high electron mobility and a well-aligned conduction band edge that facilitates rapid electron transfer from the dye molecules to the photoanode. This minimizes recombination losses and ensures a high $V_{\rm OC}$ in DSSCs. The mesoporous morphology of TiO₂ photoanodes is engineered to maximize the surface area for dye adsorption, thereby increasing light absorption and enhancing photocurrent generation. Surface modification of TiO2, such as using passivating agents or incorporating one-dimensional (1D) nanostructures like nanorods and nanotubes, further improves optoelectronic performance (detailed discussion in Section 6).48,49 1D TiO₂ nanostructures provide direct pathways for electron transport, reducing recombination and enhancing charge collection efficiency. Additionally, they enable improved light scattering and trapping, increasing the overall photon absorption within the device. Table 1 also combines all the most prominent optoelectronic features of TiO2 that are important to the DSSC application.

The anatase phase of TiO_2 is the most commonly utilized in DSSCs because it offers an optimal combination of high electron mobility, a suitable bandgap for efficient electron injection from dye molecules, and a large surface area that facilitates substantial dye loading. In contrast, the rutile phase is less frequently used on its own due to its lower electron mobility and limited surface area. However, rutile is often integrated into multi-phase systems to enhance light scattering and provide overall stability, making it a valuable component in composite structures. The brookite phase, while the least explored, presents promising intermediate properties that could be tailored for specific DSSC applications. It shows potential for performance optimization, especially when combined with anatase or

rutile. Overall, this comparison highlights how each ${\rm TiO_2}$ phase can be leveraged or modified to improve DSSC performance, depending on the desired optoelectronic and structural characteristics. $^{50-53}$

In summary, the optoelectronic properties of TiO_2 are optimized through structural and surface engineering to achieve higher light-harvesting efficiency and charge carrier dynamics in DSSCs. These advancements underscore the significance of TiO_2 in the continuous development of next-generation higherficiency solar cells, with ongoing research focused on further tuning and enhancing its performance.

6. Nano-structured 1-D TiO₂ photoanodes for DSSC

It is worth noting that the classification of photoanode materials in DSSCs is not limited to these categories and continues to evolve as new materials and approaches are developed. TiO₂ and ZnO are widely utilized materials in the fabrication of DSSCs, with TiO₂ being the preferred choice due to its superior photovoltaic applicability compared to ZnO. Despite ZnO exhibiting higher electron mobility than TiO2, DSSCs employing TiO₂ typically achieve higher efficiencies. This disparity in efficiency arises from ZnO's reduced dye adsorption capacity and its instability in acidic environments. TiO2 exists in four known polymorphs: rutile (tetragonal), anatase (tetragonal), brookite (orthorhombic), and TiO₂ (B) (monoclinic), as illustrated in Fig. 5. Among these polymorphs, anatase is favoured over rutile for photovoltaic applications, despite rutile's greater stability and lower band gap. This preference stems from anatase's higher conduction band energy level, stronger light absorption characteristics, and lower electron-hole recombination rate. The synthesis of brookite TiO2 poses challenges, making it less explored and less applicable as a photoanode material in DSSCs.54

DSSCs utilizing anatase TiO2 have demonstrated efficiencies in the range of 12-14%. As a result, TiO₂ is considered the most favourable choice as a photoanode material due to its costeffectiveness, easy availability, good stability, non-toxicity, and suitable optical and electronic characteristics. Moreover, many stable sensitizers, known for their high light absorption capability, exhibit a favourable alignment of their lowest unoccupied molecular orbital (LUMO) energy level with the conduction band of TiO2. This alignment further enhances the performance of TiO₂ photoanodes. However, the use of TiO₂ as a photoanode material also presents challenges. Firstly, TiO2 has a relatively large band gap of 3.2 eV, which results in predominant absorption in the UV region.55 Secondly, TiO2 exhibits a low internal electron transport rate. To address these challenges and improve the functionality of TiO2 photoanodes, research efforts have focused on various factors such as increasing the surface area, enhancing light scattering effects, improving interface quality, achieving fast electron mobility, and enhancing charge collection abilities. Furthermore, the physical, chemical, and optical properties of TiO2 depend not only on its intrinsic electronic structure but also on its shape, size,

Open Access Article. Published on 13 February 2025. Downloaded on 11/4/2025 6:25:21 AM.

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

()
DSSC
П
i uc
atic
plic
r ap
Q i
date
ъ
Car
suitable
Jita
a SI
ig it
makii
odes
noc
toa
ho
) ₂ p
<u>0</u>
hase
h
kite
00
ld br
аĽ
rutile,
5
atase
nat
of a
Se C
erties
ō,
al p
rica
elect
O
an.
ical
opt
cal
ypi
of i
ary
й
Sur
ч
aple
<u>–</u>

Optoelectronic features	Anatase phase TiO ₂	Rutile phase TiO ₂	Brookite phase TiO ₂	Relevance to DSSC
$\mathrm{Bandgap}\ (E_{\mathrm{g}})$	~3.2 eV	~3.0 eV	3.1–3.4 eV	Anatase's higher bandgap favours efficient charge injection but limits visible light absorption. Rutile's narrower bandgap enhances visible light harvesting, while brookite's variable bandgap offers a balance for tailored amplications.
Conduction band edge $(CB_{\rm edge})$	~-4.2 eV (vs. vacuum level)	\sim -4.0 eV (vs. vacuum level)	~~4.1 to ~4.4 eV (vs. vacuum level)	Another approximation and Anatase has a higher conduction band edge, beneficial for charge injection. Rutile's lower conduction band edge can reduce electron injection efficiency, while brookite provides a middle ground, potentially optimising both injection and
Electron mobility (μ)	0.1–4 cm 2 V $^{-1}$ s $^{-1}$ (depending on the nano-structure and synthesis method)	$\sim \! 0.1 \! - \! 1 \ \mathrm{cm^2 \ V^{-1} \ s^{-1}}$	\sim 0.5–2 cm ² V ⁻¹ s ⁻¹	Anatase has higher electron mobility, which reduces recombination losses. Rutile has relatively lower mobility, limiting performance, while brookite exhibits moderate mobility, which may be enhanced with proner envineering
Surface area (A)	\sim 50–200 m ² g ⁻¹ (mesoporous films)	\sim 20–50 m ² g ⁻¹ (lower surface area)	\sim 100–150 m ² g ⁻¹ (intermediate surface area)	Anatase's higher surface area allows for greater dye loading. Rutile, with a lower surface area, limits dye coverage, while brookite offers a compromise with moderate dye adsorption.
Light scattering	Effective at 400–800 nm, enhanced in nanostructured forms	Moderate light scattering	Effective scattering, similar to anatase	Anatase and brookite nanostructures are particularly effective in enhancing light absorption. Rutile is less effective at scattering but can still be useful when structured appropriately.
Chemical stability	Highly stable under UV and various pH conditions	Superior stability under harsh conditions	Moderately stable, less commonly studied in detail	All three phases are stable under All three phases are stable under typical DSSC conditions, but rutile is often preferred for harsh environments. Anatase remains the most widely used due to its balance of stability and performance
Nano structural versatility	Nanoparticles: 10–100 nm, nanorods: 500 nm-several µm	Nanoparticles: 50–150 nm	Nanoparticles: 20–80 nm	Anatase nanostructures (e.g., nanorods) offer efficient electron pathways, enhancing performance. Brookite's structures need further investigation, while rutile structures are often used for enhanced light scattering in composites

(c)

Fig. 5 Typical ball-stick crystal structure of TiO₂ polymorphs. (a) Anatase (tetragonal), (b) rutile (tetragonal), and (c) brookite (orthorhombic).⁵⁴

porosity, pore size distribution, organization, and surface features. Exploring and optimizing these factors contribute to the overall performance enhancement of ${\rm TiO_2}$ in DSSCs.⁵⁶

Achieving a higher dye pickup by the photoanode material leads to an increase in electron and current density generation. To enhance dye adsorption capabilities, various nanostructures of semiconductor mesoporous TiO₂, including nanorods, nanotubes, nanowires, nanosheets, and other

nanoarchitectures, have been extensively employed and investigated as shown in Fig. 6(a-f).

These nanostructures offer increased surface area, providing more binding sites for dye molecules and promoting efficient light absorption. In addition to maximizing surface area, enhancing electron mobility is crucial for improving photoanode performance. Defects present in TiO₂, particularly at grain boundaries, can act as electron traps, hampering the

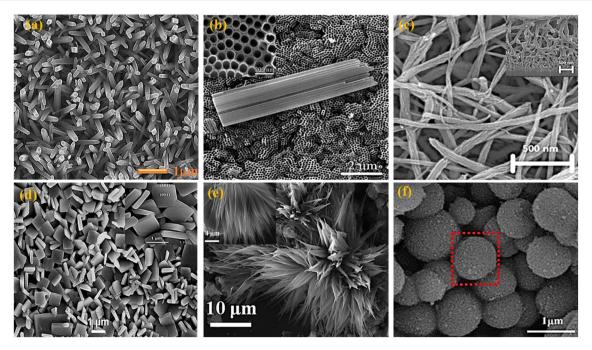


Fig. 6 FESEM images of various TiO₂ photoanodes including 1D, 2D and 3D structures explored for DSSC application. (a) Nanorods,³⁸ (b) nanotubes,⁵⁷ (c) nanowires,⁵⁸ (d) nanosheets,⁵⁹ (e) nanoflower,⁶⁰ and (f) nanoshere.⁶¹

collection of injected electrons from the semiconductor. Therefore, minimizing or eliminating defects is essential to ensure efficient electron collection and transport within the photoanode material. Surface modification techniques have also proven effective in improving the performance of ${\rm TiO_2}$ semiconductors. By modifying the surface properties, such as introducing surface coatings or functional groups, charge separation, electron mobility, and the recombination process can be significantly influenced. These surface modifications play a crucial role in facilitating efficient charge separation, reducing electron recombination, and improving overall photoanode performance in DSSCs. $^{57-61}$

Although 2D materials offer a high surface area for dye adsorption, 1D tubular structures like nanotubes and nanowires excel in charge transport and light scattering. Their elongated surface area promotes multi-path charge transport, reducing recombination losses and enhancing charge collection. Additionally, these structures provide better light scattering, improving light absorption across a broader spectrum. The 1D design enables directional charge transport along the *z*-axis, further optimizing photoanode performance. Thus, the choice of 1D tubular structures is justified by their balance of high surface area and efficient charge transport (Fig. 7).^{64,65}

The optical and electronic properties of TiO₂ are significantly influenced by its various morphologies. It has been observed

that one-dimensional nanostructures such as nanowires, nanorods, and nanotubes exhibit superior charge transport properties compared to assemblies of TiO2 nanoparticles. However, these one-dimensional structures possess a smaller surface area than nanoparticle systems, resulting in reduced dye adsorption capability. To address this limitation, the introduction of dopants with enhanced dye adsorption capacities can improve the photovoltaic performance of onedimensional nanostructures.66 This allows for better utilization of incident light and improved conversion of photons into charge carriers. On the other hand, nanoparticle assemblies can benefit from dopants that promote increased charge transfer processes. These dopants facilitate efficient electron transfer between the TiO2 nanoparticles, enhancing the overall conductivity and charge transport within the material. As a result, it becomes challenging to determine the precise contribution of absorption enhancement or electronic effects in doped TiO₂ towards the improvement of its performance. Both factors, the increased absorption of light due to enhanced dye adsorption and the improved charge transfer properties resulting from dopants, play a crucial role in enhancing the overall photovoltaic performance of doped TiO₂ materials.⁶⁷

Nanotubes, nanowires, nanofibers, nanobelts, and nanoribbons are a few examples of one-dimensional nanostructures that have found extensive use in DSSCs. The ground-breaking

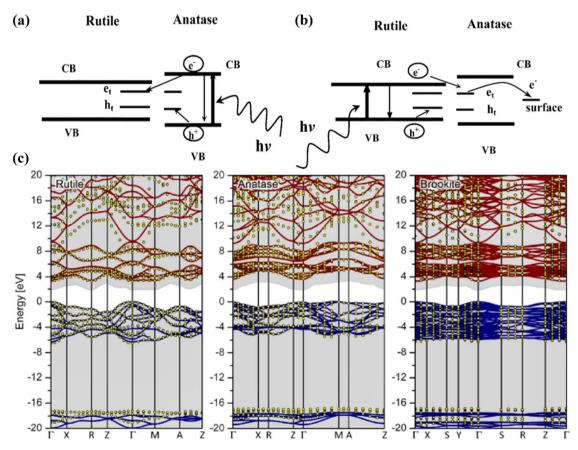


Fig. 7 (a and b) Typical schematics of charge trapping process in two-phase TiO_2 namely rutile and anatase, which illustrate that photogenerated charges in the anatase phase can be further trapped *via* injection in the rutile phase, ⁶² (c) typical band structures and quasi-particle energies of different TiO_2 phases (Rutile, Anatase, Brookite). ⁶³

research by Iijima *et al.* is largely responsible for the growing interest in these nanomaterials.⁶⁸ For electron transport from the semiconductor layer to the conducting substrate, their orderly alignment provides an identifiable route. This has two effects: first, it slows down the rate of electron recombination, and second, it improves the solar cell's efficacy.

6.1. 1-D TiO₂ nanowires

In DSSCs, TiO₂ nanowire (TNW) architectures are significant because they function as constrained conducting channels with long charge diffusion lengths that efficiently avoid charge

recombination and promote optimal charge transport. They are now considered to be potential candidates for use in the manufacture of DSSC due to their special characteristics. When used as dye scaffolds, a dense array of long, thin nanowires can dramatically improve both dye absorption and carrier collecting efficiency. Additionally, nanowire photoanodes show superior compatibility with unconventional electrolytes such solid inorganic phases or polymer gels, which normally have greater recombination rates (Fig. 8).⁶⁹

The electron-hole recombination time and electron collection time ratio of TNW-based DSSCs are exceptional, being

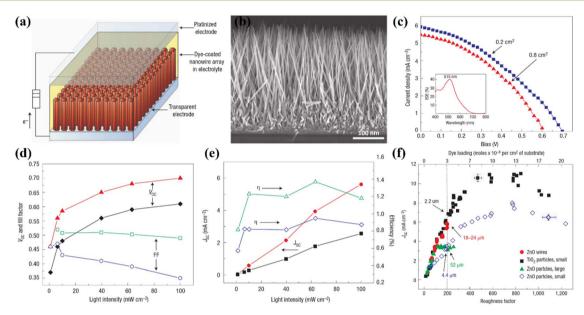


Fig. 8 (a) Schematic DSSC fabricated using TiO_2 nanowires as a photoanode, (b) typical FESEM image of cross-sectional view of TiO_2 nanowires, (c) J-V analysis of respective DSSC with two different active area of 0.2 cm^2 and 0.8 cm^2 along with quantum efficiency curve shown inset, (d and e) trace of V_{OC} , FF, J_{SC} , and η against light irradiance, (f) comparative analysis of DSSC prepared using nanoparticles and nanowires with respect to roughness and dye-loading.⁶⁹

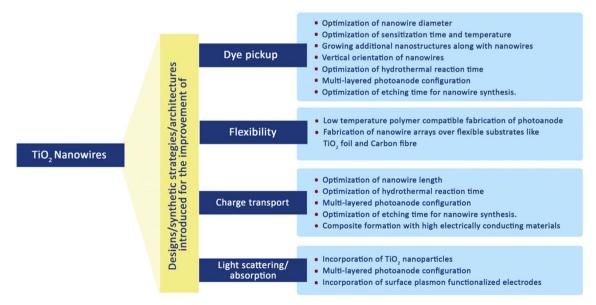


Fig. 9 Various modifications made in TiO₂ nanowires to improve the DSSCs performance.⁷⁰

around 150 times higher than those of nanoparticle-based solar cells. This substantial variation emphasises the higher collecting efficiency attained with nanowire arrays. The various initiatives made to improve the critical aspects affecting the overall efficiency of TNW-based DSSCs are summarised in Fig. 9.70

Feng *et al.* introduced a simple technique for producing single-crystalline rutile TNWs at low temperatures. The method involves a nonpolar solvent and a hydrophilic solid substrate interfacial reaction under hydrothermal conditions. Using this approach, they were able to grow vertically aligned nanowires with lengths of up to 5 μ m on TCO glass substrates. When N719 dye was applied to the TNW arrays measuring 2–3 μ m in length, the system achieved an efficiency of 5.02% under AM1.5 irradiation. Tonsequently, the implementation of low-temperature techniques for photoanode fabrication is

compatible with polymer substrates, enabling enhanced flexibility in the process. A hydrothermal technique capable of precisely creating TNW arrays on a titanium mesh with an average diameter of 80 nm was presented by Liu *et al.* (2015). They investigated the influence of sensitization temperature and time on the performance of TNW arrays in DSSCs. They observed that higher sensitization temperatures enhanced dye infiltration into the internal regions of the TNW films, leading to improved photovoltaic performance. Under optimal conditions, they achieved an efficiency of 3.42% for a flexible DSSC, demonstrating effective dye coverage and reduced charge recombination (Fig. 10(f-g)).⁷² Additionally, in addition to attaining the intended dye uptake, their method also effectively reduced charge recombination problems.

In contrast, Bakshayesh *et al.* employed a corn-like nanowire structure fabricated through a surface tension stress

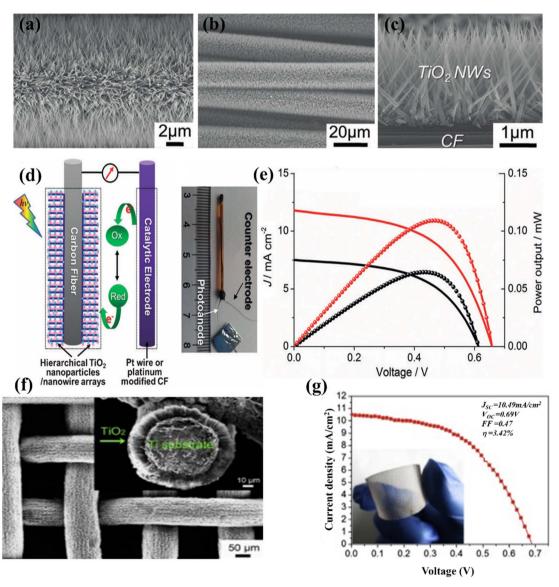


Fig. 10 (a–c) FESEM images of hierarchical TiO_2 nanowire arrays grown over the CF substrate at 190 °C for 80 minutes, (d and e) schematic of wire DSSC consisting TiO_2 nanoparticle and nanowires and Pt-modified CF counter electrodes and consequent J-V analysis, (f and g) low-magnification FESEM images of the TiO_2 NWAs on Ti mesh substrates and respective J-V performance.⁷²

mechanism, achieving a dual-layer photoanode comprising a bottom layer of anatase TiO₂ nanoparticles and a top layer of corn-like TNWs. This design enhanced light scattering, dye sensitization, and charge carrier generation, resulting in a higher efficiency of 7.11%. The increased surface area of cornlike nanowires significantly improved dye uptake and I_{SC} , while the nanoparticles further amplified light scattering, boosting overall device performance.73 Zha et al. focused on controlling the length of the nanowires, producing 6 µm long TNWs through an 8 hours synthesis process. This approach highlighted the critical role of microstructural properties in DSSC efficiency, with their system achieving a notable efficiency of 5.61%.⁷⁴ Building on this, Wu et al. demonstrated the potential of vertically aligned TNWs with lengths adjustable between 15 and 55 µm for multi-layered photoanode configurations. By sensitizing these TNWs with N719 dye, they achieved an impressive efficiency of 9.40% (Fig. 11(a-e)), underscoring the importance of controlled nanowire alignment and length in enhancing light harvesting and charge transport in DSSCs.75

A unique DSSC created by Yen et al. successfully integrated plasmonic and antireflective properties. Their DSSC included a 3D TNW-AuNP plasmonic electrode made up of Au nanoparticles (NPs) attached to antireflective TNWs, which served as light-harvesting antennae. The absorption wavelength was increased from 520 nm to 575 nm as a result of the use of plasmonic functionalized electrodes (PFEs). This strategy intended to get beyond the drawbacks of standard DSSCs' small dye absorption ranges and poor dye absorption coefficients. TiCl₄ treatment was used to further improve the TNW-Au-NP hybrid DSSCs' efficiency, leading to a notable improvement from 6.25% to 9.73%. It was shown that combining antireflective qualities with plasmonic effects was a successful way to boost the efficiency of DSSC.76

In their study, Wu et al. established a distinctive and inventive architecture by integrating various three-dimensional, hyperbranched titania nanostructures in a multi-stack configuration. The photoanode design comprised of three layers: a bottom layer composed of hyperbranched hierarchical treelike titania nanowires, an intermediate layer featuring branched hierarchical rambutan-like titania hollow sub-micrometer-sized spheres, and a top layer encompassing hyperbranched hierarchical urchin-like titania micro-meter-sized spheres. Each layer had a distinct function that improved the photoanode's overall performance. Efficient electron transport from 1-D nanowires to the FTO plate was made possible by the bottom layer. Due to the hollow-hole structure of the sub-micrometer-sized macro-porous TiO2 spheres, the intermediate layer provided excellent light-trapping efficiency. On the other hand, more light might be scattered thanks to the higher layer of hyperbranched hierarchical TiO2 microspheres. The combination of these various nanoarchitectures produced an astounding photoanode efficiency of 11.01%, outperforming its TiO₂ nanoparticle counterpart appreciably.⁷⁷ The creation of outstanding performance photoelectrochemical devices for a variety of applications is greatly enhanced by this research. The previous discussion highlighted the substantial endeavors that were undertaken to enhance the performance of nanowirebased DSSCs, and a summary of these efforts is provided in Table 2.

6.2. 1-D TiO₂ nanorods

In order to improve the efficiency of DSSCs through the use of their special 1-D nanoscale properties, nanorods (NRs) have been introduced into the fabrication process of DSSCs. Due to their unique geometry, these TNRs have benefits in enhancing effective electron transport. The DSSCs can perform better overall by integrating TNRs because they can lessen the ohmic loss that ordinarily happens during the electron transfer process through the mesoporous titania layer. Researchers have looked into numerous processes for creating TNRs exclusively for DSSC applications in order to acquire the needed characteristics. Additionally, as illustrated in Fig. 12, they have worked very hard to change the morphology and surface characteristics of these nanorods.70 These efforts include the development of novel synthesis techniques that allow TNRs to be customized to

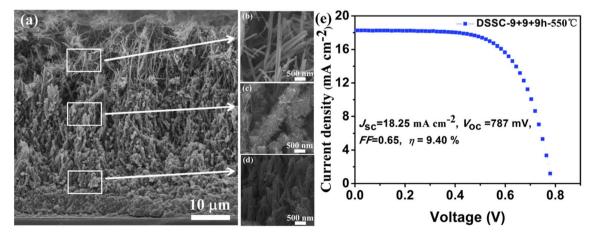


Fig. 11 (a) Cross-sectional FESEM image of TiO₂ nanowires grown on FTO substrate in 3 cycles of 9 h each, (b-d) FESEM images of top, intermediate, and bottom layers of grown nanowires, (e) J-V analysis of the DSSC prepared using these TiO₂ nanowires having total thickness of 47 μm.⁷⁵

Table 2 Comparative analysis of DSSCs fabricated via TiO2 nanowire photoanodes and their performance

Photoanode type	Dye	Electrolyte	PCE	Ref.
Vertically aligned single-crystalline TiO ₂ nanowire arrays by nonpolar solvent/ hydrophilic solid substrate interfacial reaction under hydrothermal conditions	N719	MPN-100 (Solaronix, Inc., Switzerland) containing tri-iodide in methoxy–propionitrile	5.02%	71
Double-layered photoanode having corn- like TiO ₂ nanowires prepared by a surface tension stress mechanism	N719	Dimethylpropylimidazolium iodide, LiI, I_2 , and 4-tert-butylpyridine in acetonitrile	7.11%	73
Thornbush-like ${\rm TiO}_2$ nanowires (TBWs) prepared by a facile single-step hydrothermal method	N719	Dimethylpropylimidazolium iodide, LiI, I_2 , and 4 -tert-butylpyridine in acetonitrile	6.7%	78
Double-sided brush shaped (DSBS) TiO ₂ nanoarchitecture consisting of highly ordered TiO ₂ nanowires aligned around an annealed TiO ₂ nanoparticle layer was prepared by a hydrothermal method	N719	1-Butyl-3-methyl imidazolium iodide, I ₂ , guanidinium thiocyanate, and 4- <i>tert</i> -butylpyridine in a mixture of acetonitrile and valeronitrile	5.61%	74
Vertically aligned anatase TiO ₂ nanowires on FTO glass with a tunable length in the range of 15–55 mm for multilayered configuration of the photoanode by a hydrothermal method	N719	${ m I}^-/{ m I}_3^-$ redox electrolyte	9.40%	75
Photoelectrode with multi-stacked layers having integrated functions	N719	1-Methyl-3-propylimidazolium iodide (PMII), LiI guanidinium thiocyanate, I ₂ , and <i>tert</i> -butylpyridine in acetonitrile and valeronitrile	11.01%	77
Vertically aligned rutile TiO ₂ nanowire arrays (NWAs) by a single-step solvothermal method without using any surfactant or template	C106	DMII, LiI, I_2 , TBP, and GNCS in the mixture of acetonitrile and valeronitrile	8.9%	79
3D TNW-AuNP plasmonic electrode prepared by hydrothermal and sputtering techniques	N719	${\rm I_2,LiI,DMPII,andTBPinacetonitrile}$	9.73%	76
Rough surface rutile TiO ₂ nanowire array prepared by a hydrothermal method and prolonged etching. An additional light-scattering layer of TiO ₂ particles was also employed	C109	1,3-Dimethylimidazolium, lithium iodide, iodine, <i>tert</i> -butylpyridine, and guanidinium thiocyanate in acetonitrile and valeronitrile	9.39%	80

match the unique needs of DSSCs and further increase their efficacy.

In order to exert control over the size and diameter of the nanorods, Jiu et al. in 2006 successfully synthesised singlecrystalline anatase TNRs using a surfactant-assisted hydrothermal method. The resultant nanorods had a length that ranged from 100 to 300 nm and a diameter of 20 to 30 nm. The incorporation of these TNRs into DSSCs allowed the researchers to obtain a noteworthy efficiency of 7.29%.81 Because it permitted for improved electron transport qualities and more effective light absorption, the ability to adjust the size and diameter of the nanorods played a vital part in their efficacy within the DSSCs and eventually contributed to the better overall efficiency of the DSSC. This work by Jiu et al. opened up new opportunities for further developing solar cell technology by demonstrating the potential of using TNRs in DSSC photoanodes. De Marco et al. achieved a PCE of 7.9%, which represents a significant improvement in the performance of DSSCs. The utilization of TNRs, which were made using a single-step solvothermal method, allowed this substantial improvement.

The produced anatase TNRs were afterward turned into a screen printable paste, making it simple to apply to DSSCs.⁸²

Zhang et al. in their work suggested a unique method for fabricating anatase TNRs with controllable dimensions and shapes. They were able to create long, single-crystalline TNRs with reduced grain boundaries that improved charge collecting by using an orientated attachment technique. These long, skinny NRs of average thickness of 16 \pm 0.5 μm allowed DSSCs to operate at an amazing 8.87% efficiency.83 Parallelly, Liu et al. created a solvothermal technique to create single-crystalline anatase TNRs using tetrabutylammonium hydroxide (TBAH) as a morphology-controlling agent. The DSSCs created with the help of these nanorods with thicknesses varying from 6.2 to 14.8 μm had a noteworthy PCE of 8.66% (Fig. 13(a and b)).84 A notable development in DSSCs was made in 2009 by Lee et al., who attained a remarkable efficiency of 9.52%, as shown in Fig. 13(c and d). They used a hybrid of electrospinning and solgel methods to create TNRs from a solution of polyvinyl acetate and titanium n-prop-oxide in dimethyl formamide. They compared the performance of DSSCs based on nanoparticles and nanorods of average diameters of ~15 nm and lengths of

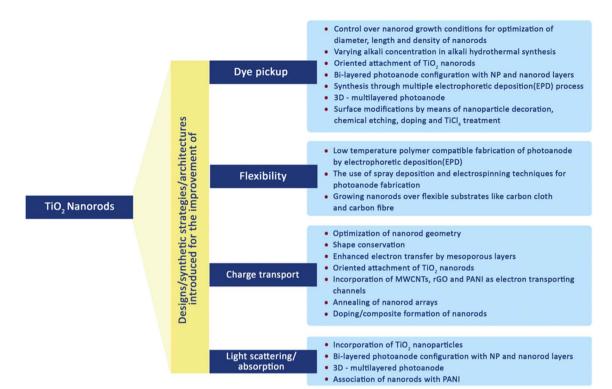


Fig. 12 Various modifications made in TiO₂ nanorods to improve the DSSCs performance.⁷⁰

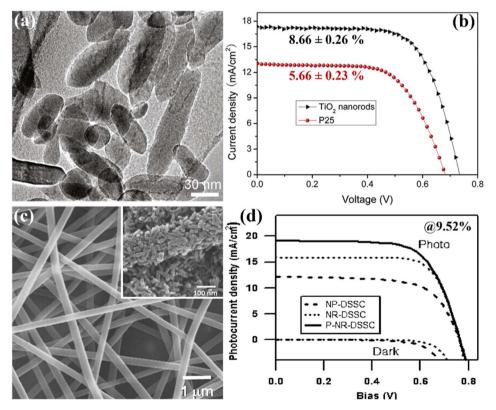


Fig. 13 (a and b) High resolution TEM image of single crystalline anatase TiO_2 nanorods and the respective DSSC performance with 8.66% PCE, ⁸⁴ (c and d) typical SEM image of electro-spun TiO_2 -PVAs nanofibers with heat treated @400 °C SEM image in inset and their consequent performance with PCE of 9.52%. ⁸⁵

60-100 nm. Through their research, they noticed that the pore volume of the TNR-DSSCs was double that of the nanoparticle-DSSCs. When compared to nanoparticle-based DSSCs with comparable masses of TiO2, the TNR-based DSSCs had almost 2.5 times as much surface area accessible as sensitizers.85 Additionally, nanorods showed an 8-times prolonged electronhole recombination time than nanoparticle DSSCs, indicating greater charge separation and retention. Multi-walled carbon nanotubes (MWCNTs) were incorporated into TNRs with an optimum thickness of 14.3 \pm 0.3 μm using the electrospinning method in 2013, which Yang et al. dubbed "electron transporting superhighways". The inventive addition of MWCNTs improved the DSSCs' efficiency even more, increasing it to an astonishing 10.24%.86

Table 3 Comparative analysis of DSSCs fabricated via TiO₂ nanorod photoanodes and their performance

Photoanode type	Dye	Electrolyte	PCE	Ref.
${ m TiO_2}$ single crystalline anatase nanorods prepared by a surfactant-assisted hydrothermal method	N719	LiI, 1,2-dimethyl-3- <i>n</i> -propylimidazolium iodide (DMPII), I ₂ , and 4- <i>tert</i> -butylpyridine (TBP) in methoxyacetonitride	7.06%	90
Highly crystalline TiO ₂ nanorods synthesized by a hydrothermal process in a cetyltrimethylammonium bromide surfactant solution	N719	LiI, 1,2-dimethyl-3- n -propylimidazolium iodide (DMPII), I ₂ , and 4- $tert$ -butylpyridine (TBP) in methoxyacetonitride	7.29%	81
TiO ₂ nanorod based photoelectrodes prepared by a combination of sol-gel chemistry and electrospinning	N719	1-Butyl-3-methylimidazolium iodide, iodine, guanidinium thiocyanate, and 4-tert-butylpyridine in acetonitrile/ valeronitrile	9.52%	85
TiO ₂ anatase nanorods prepared by a simple one-step solvothermal method	N719	LiI, I ₂ , 1-methyl-3-propylimidazolium iodide, and <i>tert</i> -butylpyridine in dried acetonitrile	7.9%	82
1:1 TiO ₂ NR-NP composites prepared by a hydrothermal technique with a hydrogen titanate nanorod precursor	N719	LiI, ${\rm I_2}$ and $4\text{-}t\text{-}{\rm butylpyridine}$ in acetonitrile	8.61%	91
Ultraporous anatase ${ m TiO_2}$ nanorods fabricated by a simple microemulsion electrospinning approach	N719	I ₂ , LiI, 1-methyl-3-propylimidazolium iodide (PMII), guanidinium thiocyanate, and <i>tert</i> butylpyridine in a mixture of acetonitrile/valeronitrile	8.53%	92
TiO ₂ microspheres assembled by single crystalline rutile TiO ₂ nanorods were synthesized by one-pot solvothermal treatment	N719	I ₂ , LiI, 1-methyl-3-propylimidazolium iodide (PMII), guanidinium thiocyanate, and <i>tert</i> -butylpyridine in a mixture of acetonitrile/valeronitrile	8.22%	93
MWCNTs are introduced into TiO ₂ nanorods by electrospinning	N719	I ₂ , LiI, 1-methyl-3-propylimidazolium iodide (PMII) and 4- <i>tert</i> -butylpyridine in a mixture of acetonitrile/ valeronitrile	10.24%	86
Single crystal-like anatase TiO ₂ nanorods with a specific growth direction are prepared by a hydrothermal method	Z 907	1,3-Dimethylimidazolium iodide, LiI, and ${\rm I_2}$ in a mixture of acetonitrile and valeronitrile	8.87%	83
Single-crystalline anatase TiO ₂ nanorods were prepared by a solvothermal method	N719	LiI, I ₂ , dimethylpropylimidazolium iodide (DMPImI) and <i>tert</i> -butylpyridine in dry acetonitrile	8.66%	84
Monodispersed TiO ₂ nanorods were prepared using a simple solvothermal process	N719	Lithium iodide, iodine, 4- <i>tert</i> - butylpyridine and 1,2-dimethyl-3- propylimidazolium iodide was dissolved in acetonitrile	9.21%	94
Single-crystalline anatase ${ m TiO_2}$ nanorods with a high aspect ratio	N719	LiI, I ₂ , dimethylpropylimidazolium iodide (DMPImI) and <i>tert-</i> butylpyridine in a dry mixed solution	7.51%	89
Double layered photoanode having an overlayer of a TiO_2 NR array and underlayer of a TiO_2 embedded ZnO nanoflower array by a sol–gel method	N719	LiI, I_2 and LiClO $_4$ in acetonitrile	8.01%	87
Rutile TiO_2 nanorods incorporated with α alumina were developed on an FTO surface via a hydrothermal route	N719	KI, I_2 and 4-tert-butyl pyridine	6.5%	95

Review RSC Advances

There was subsequently a rise in interest in fusing other nanomaterials with TiO₂ nano-morphologies. One such notable photoanode material has a double-layered structure with ZnO nanoflowers embedded in TiO2 as the bottom layer and TNRs as the top layer. Chen et al. successfully achieved a PCE of 8.01% by using optimized 10 μm thick ZNFs@TNPs + TNR integrated photoanodes. This innovation demonstrates the investigation of innovative nanomaterial combinations to improve photoanode performance for possible use in photovoltaic devices.87 Subramaniam et al. succeeded in overlaying the TNR surface with a layer of reduced graphene oxide (rGO) to increase the nanorods' charge collection efficiency. An outstanding PCE of 4.54% was achieved because of the addition of a 2 wt% rGOloaded nanocomposite, which greatly increased photoconversion efficiency.88 Later studies by Tang and team revealed a connection between the efficacy and ability of dye loading on TNRs and their aspect ratios. They discovered that the dye loading efficiency and capacity both rose when the NRs' aspect ratios did. They managed the response time during the preparation procedure to produce nanorods with various aspect ratios.89 Significant results from numerous investigations on TNR-based DSSCs are compiled in Table 3.

6.3. 1-D TiO₂ nanotubes

 ${
m TiO_2}$ nanotubes (TNTs), which have a distinctive hollow cavity architecture and a much greater active surface area, were the subject of research. TNTs generally showing exceptional abilities in terms of increased absorption capacity and quick electron transport, making them particularly appropriate for use in DSSCs. ${
m TiO_2}$ meso-structures can successfully avoid the emergence of electron traps by using nanotube arrays with small spaces between them. The diffusion length, which measures the distance an electron may travel inside a tube before engaging in

recombination, is significantly improved as a result of this estimated strategy. According to calculations, a nanotube cell's diffusion length is approximately 100 μm.96 In order to increase the surface area while also lowering the likelihood of recombination, the size of the nanotubes can be extended up to this threshold. TNTs have some disadvantages, chief among them being the high cost of production and the time-consuming preparatory procedures needed. The morphology and crystalline structure of the TNTs used in DSSCs significantly impact their efficiency. Contrary to popular belief, it has been found that decreasing tube diameter has a greater positive influence on efficiency improvement than increasing tube length. The annealing temperature that the nanotubes go through also affects how much dye is put into them. Harvesting efficiency is another important aspect that affects performance, and it can be improved by making changes to the tube surfaces that reduce recombination losses.97 The efforts made to improve the efficiency of TNT-based DSSCs are shown in Fig. 14.70

A study by Wang *et al.* showed that a 14 μm elongated TNT array in DSSCs can be made more effective by being treated with TiCl₄ and ozone. They attained an efficiency of 7.37% by using this surface engineering strategy, as shown in Fig. 15(a and b).⁹⁸ Similar to this, Lei *et al.* used an optimized 20.8 μm length of 1-D TNT arrays made by anodization to reach an efficiency of 8.07% (Fig. 15(c and d)).⁹⁹ Another study by Hun Park *et al.* revealed that after undergoing treatment with TiCl₄, TNTs longer than 15 μm that were transplanted onto an FTO plate had a PCE of 5.36%.¹⁰⁰ Researchers looked into adding dopants to TNT arrays alongside surface engineering to increase performance. They intended to obtain an ideal alignment between the LUMO of dye molecules and the conduction band of TNTs in order to facilitate effective electron transfer. This alignment was predicted to improve electron injection and

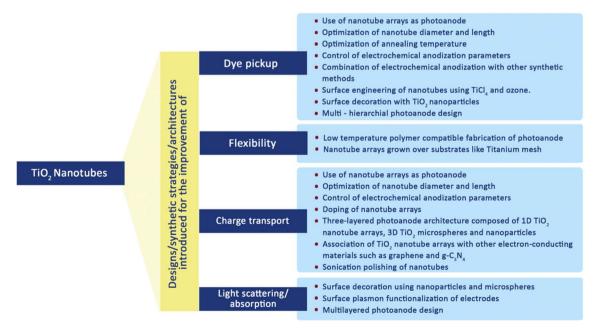


Fig. 14 Various modifications were made to the TiO₂ nanotubes to improve the DSSC's performance.⁷⁰

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 13 February 2025. Downloaded on 11/4/2025 6:25:21 AM.

RSC Advances

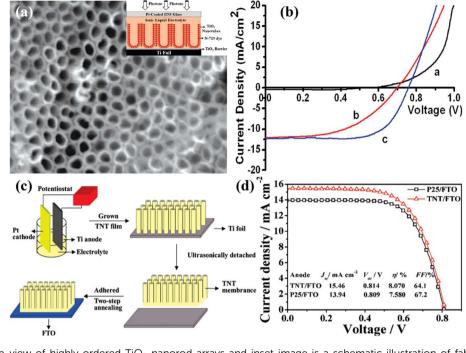


Fig. 15 (a) FESEM top-view of highly ordered TiO_2 nanorod arrays and inset image is a schematic illustration of fabricated DSSC, (b) J-Vcharacteristics of the prepared device (black: under dark light, red: without TiCl₄ treated anatase TiO₂ nanotube array, and blue: TiCl₄ treated TiO_2 based DSSCl, ⁹⁸ (c) schematic procedure of fabricating crystallized TiO_2 nanotubes on FTO substrate, (d) Comparative J-V analysis using the same thickness (20.8 μ m) of TiO₂ nanotubes/FTO film and P25/FTO film under AM 1.5G illumination (100 mW cm⁻²).99

decrease electron recombination, improving overall efficiency. Numerous research teams investigated other strategies for doping to improve TNT arrays in DSSCs, such as surface decorating with nanoparticles and microspheres. It was shown by Roy et al. that treating TNTs with TiCl₄ caused the TNT surface to be decorated with TiO₂ nanocrystals. The overall efficiency was raised as a result of the much-increased dye absorption

provided by the surface ornamentation.¹⁰¹ He et al. used microwave-created TiO2 microspheres to decorate a TiO2 NTA with a total thickness of 17.4 µm. This method can potentially improve the functionality of DSSCs because adding these microspheres led to an efficiency of 7.24%.102

Fu et al. accomplished a substantial development by creating an intriguing multi-hierarchical photoanode with a cigar-

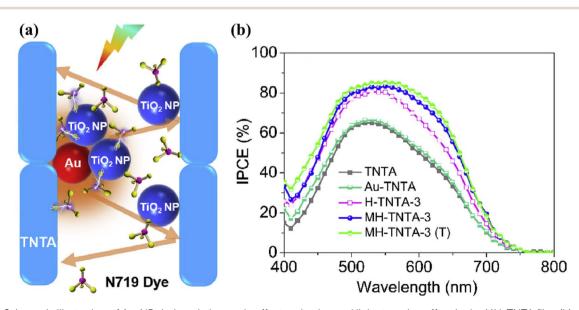


Fig. 16 (a) Schematic illustration of Au-NPs induced plasmonic effect and enhanced light-trapping effect in the MH-TNTA film, (b) consequent IPCE spectra of DSSCs based on various photoanodes. 103

shaped Au/TiO2 NTR/TiO2 nanoparticle structure in 2019. This photoanode with a thickness of 15.2 µm had an amazing PCE of 8.93% (Fig. 16(a and b)).103 A novel vacuum-assisted colloid filling method was used to develop this one-of-a-kind multihierarchical design, which led to a photoanode with four times better charge transfer and 3.2 times greater dye intake than standard TNT array-based photoanodes. A hybrid photoanode that combines ZnO nanorods with TNTs having 90 nm inner diameter and ~4 µm length was proposed by Bozkurt et al. in a different work. 104 This hybrid photoanode was created using a two-step synthetic procedure that started with the anodic oxidation of TNTs and ended with the hydrothermal layering of ZnO nanorods on top of the TNTs. This hybrid strategy shows promise in improving photoanode effectiveness for prospective use in DSSC. Comparing the hybrid design to the conventional TNT photoanode, the PCE was increased by around a factor of two.

A ground-breaking 3-layered photoanode structure of 1D TNT-arrays, 3D TiO₂ microspheres, and 0-D nanoparticles was developed by Wu et al. in 2014. This creative design displayed outstanding inherent characteristics, such as a high dye loading capacity, effective light scattering performance, and improved charge collection ability. These beneficial characteristics allowed this innovative structure to achieve an unparalleled 9.10% PCE.105 In order to further investigate and improve their performance, multiple other research groups have imitated this technique by producing tri-layered photoanodes with a variety of changes. In general, many techniques for altering TNTs have been employed, which includes (a) gluing on light-harvesting molecules for sensitization of nanotubes, (b) doping with multiple components, (c) band gap tuning, (d) developing electronic heterojunctions, and (e) furnishing with additional semiconductor particles.106 An overview of the many uses of tubular TiO₂ nanoparticles in DSSCs is given in Table 4.

Table 4 Comparative analysis of DSSCs fabricated via TiO₂ nanotubes photoanodes and their performance

Photoanode type	Dye	Electrolyte	PCE	Ref.
Titania nanotubes were synthesized using molecular assemblies	N3	0.03 M iodine in 0.3 M lithium iodide in 3-methyl-2-oxazolidinone (NMO)/acetonitrile	4.88%	107
Highly ordered TiO ₂ nanotube arrays were fabricated by electrochemical anodization followed by surface engineering using TiCl ₄ and O ₂ plasma	N719	BMIM-I, I_2 , TBP, and GTC in acetonitrile/valeronitrile	7.37%	98
Highly ordered one-dimensional TiO ₂ nanotube arrays were prepared by anodization of pieces of Ti foil	N719	I ₂ , 1-methyl-3-propylimidazolium iodide (PMII), guanidinium thiocyanate, and tert- butylpyridine in acetonitrile and valeronitrile	8.07%	99
Layer-by-layer assembly of self-standing titania nanotube arrays and NPs were prepared by anodization	Ru535-bisTBA	1,2-Dimethyl-3-propyl imidazolium iodide, LiI, ${\rm I}_2$, and 4- $tert$ -butylpyridine in acetonitrile	8.80%	108
TNTAs were prepared by anodization of pieces of Ti foil in an aqueous solution containing hydrofluoric acid and TiO ₂ scattering microspheres were prepared <i>via</i> a microwave solvothermal process	N719	I ₂ , 1-methyl-3-propylimidazolium iodide (PMII), guanidinium thiocyanate, and <i>tert</i> - butylpyridine in a solution of valeronitrile and acetonitrile	7.24%	102
Double layered photoanode with a 1D NT underlayer and 3D hierarchical upper layer was prepared by a hydrothermal method and then incorporated with hydrothermally prepared TiO ₂ NPs	N719	1-Methyl-3-propylimidazo-lium iodide (PMII), guanidinium thiocyanate, $\rm I_2$, LiI, and tert-butylpyridine dissolved in acetonitrile and valeronitrile	9.10%	105
TiO ₂ NTAs prepared by anodization were transplanted on to a P25 coated FTO plate and then flower like TiO ₂ prepared hydrothermally was deposited over a P25/	N719	LiI, I_2 , 4-tert-butylpyridine and 1, 2-dimethyl-3-propylimidazolium iodide (DMPII) in dry acetonitrile	6.48%	109
"Cigar-like" Au/TiO ₂ -nanotube-array/ TiO ₂ -nanoparticle multi-hierarchical photoanode through a novel vacuum- assisted colloid-filling approach	N719	LiI, $\rm I_2$, 1-methyl-3-hexylimidazolium iodide (HMII), <i>N</i> -methylbenzimidazole (NMB) and 4-tert-butylpyridine in 3-ethoxypropionitrile	8.93%	103
Tri-layered photoanode consisting of single crystal hollow TiO ₂ nanoparticles (HTNPs), sub-micro hollow TiO ₂ mesospheres (SHTMSs) and hierarchical TiO ₂ microspheres (HTMSs)	N719	1-Methyl-3-propylimidazo-lium iodide (PMII), guanidinium thiocyanate, I ₂ , LiI, and <i>tert</i> -butylpyridine dissolved in acetonitrile and valeronitrile	9.24%	110
Open ended TiO ₂ nanotube array photoanode was prepared by fast removal of bottom caps by mechanical ball milling	N719	LiI, I_2 , 1-methyl-3- hexylimidazolium iodide (HMII), <i>N</i> -methylbenzimidazole (NMB), and 4-tert-butylpyridine in 3-methoxypropionitrile	7.7%	111

6.4 Engineered TiO₂ photoanodes for DSSC

TiO₂ photoanodes are critical to the performance of DSSCs, providing a high surface area for dye adsorption, efficient electron transport, and effective charge separation. The material's wide bandgap, high electron mobility, and chemical stability make it well-suited for this role. However, optimizing the crystalline phase, morphology, and surface properties of TiO₂ is essential to enhance light harvesting, reduce recombination losses, and maximize efficiency. This section explores the engineered optoelectronic features of TiO₂ photoanodes and their impact on DSSC performance.

6.4.1. Doping. Doped TiO₂ has become crucial for enhancing the efficiency and performance of DSSCs. Incorporating various doping elements, such as transition metals and carbon, has been extensively studied to optimize the electronic properties of TiO2, resulting in improved charge transfer and enhanced light absorption. Doping in the TiO2 lattice can effectively modify its electronic properties through the intentional introduction of impurities. By incorporating dopants into the TiO₂ structure, the number of free charge carriers and the overall conductivity of the material can be increased. This phenomenon arises from the inherent presence of defects within the TiO2 lattice, which directly influence the electronic structure and the occurrence of trap states within the material (Fig. 17(a)).62,63 During the doping process, either the Ti⁴⁺ cations or the O^{2-} anions can be substituted with other atoms. Consequently, the replacement of Ti⁴⁺ cations or O²⁻ anions leads to alterations in the conduction band (CB) and valence band (VB) structures, respectively. The CB energy levels are primarily formed by the orbitals of Ti4+ ions, while the VB

energy levels predominantly consist of the O^{2-} 2p orbitals (Fig. 17(b)). 112,113

Doping of TiO₂ nanoparticles has been observed to have a significant effect on their growth rate, resulting in the formation of smaller particles with a greater surface area compared to undoped TiO₂. This inhibition of growth can be attributed to the presence of dopant atoms within the TiO₂ lattice, which introduce defects and alter the crystal structure, thereby hindering the crystal growth process. The increased surface area of doped TiO₂ nanoparticles offers several advantages. Firstly, it enhances the adsorption capacity of dyes onto the TiO₂ surface, leading to improved performance in applications such as DSSCs. The larger surface area provides more active sites for the dye molecules to attach, promoting efficient light absorption and conversion.¹¹⁴

Recently, Ju et al. demonstrated that doping TiO2 with transition metals (Cu and Zr) via a sol-gel method enhances the energy conversion efficiency of DSSCs. The doping extends light absorption into the visible region, improving electron generation and conductivity. Further, EIS and IMPS/IMVS analysis show reduced electron-transfer resistance and enhanced electron mobility, speed, and lifetime. As a result, Cu, Zr doping increases DSSC efficiency by 3.28%.115 TiO2 mesoporous structures were doped with indium (In) using a sol-gel method to enhance their performance as photoanodes in DSSCs, which was explored by Ayaz and the group. In-doping increased carrier concentration $(1.1 \times 10^{17} \text{ cm}^{-3})$, conductivity, and charge transfer properties, as confirmed by Mott-Schottky and EIS, which showed reduced charge transfer resistance (33 Ω cm²). The TiO₂: In-based DSSC achieved an 8.62% efficiency, a 55% improvement over non-doped TiO2. 116 In another report, Sharif

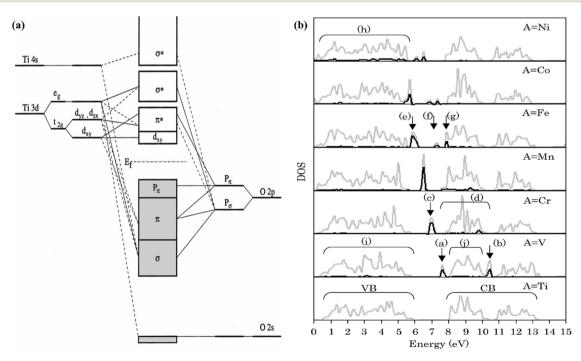


Fig. 17 (a) Detailed molecular orbital bonding diagram of TiO_2 composed of the components extracted from the DOS spectra, ¹¹² (b) density of states (DOS) of $Ti_{1-x}A_xO_2$ doped *via* various metals (A: V, Cr, Mn, Fe, Co, Ni) where grey lines and black lines representing total DOS and dopant DOS respectively. ¹¹³

Review RSC Advances

 $et\ al.$ synthesized Ag-doped TiO $_2$ nanomaterials (1–4% Ag) using a green-modified solvothermal method and tested them as photoanodes in DSSCs. The 4% Ag-doped TiO $_2$ exhibited enhanced photovoltaic performance, with a $J_{\rm SC}$ of 8.336 mA cm $^{-2}$, $V_{\rm OC}$ of 698 mV, FF of 0.422, and a PCE of 2.45%, significantly outperforming 2% Ag-doped TiO $_2$ (PCE of 0.97%) and pristine TiO $_2$ (PCE of 0.62%). Ag doping improved charge transport, reduced charge recombination, and enhanced the optical, structural, and electrochemical properties, leading to better device performance. 117

Moreover, TiO₂ doped with C and co-doped with Zn (Zn–C) and Sn (Sn–C) were prepared *via* sol–gel methods and tested as photoelectrodes in DSSCs by Nursam *et al.*¹¹⁸ The doping reduced TiO₂ crystallite size and bandgap. The DSSC with undoped TiO₂ achieved 3.83% efficiency, while C-doped TiO₂ improved to 4.20%. However, Zn–C and Sn–C co-doped TiO₂, resulting in lower efficiencies of 0.71% and 0.85%, respectively. Rajaramanan *et al.* present a method for fabricating nitrogendoped TiO₂ (N-doped TiO₂) photoanodes for DSSC applications. N-doping was achieved by grinding NH₄OH with P25–TiO₂, followed by calcination at 500 °C. The optimized 20N–TiO₂, with 20 μL NH₄OH, showed a pore diameter of 15.99 nm and a reduced bandgap of 2.94 eV. The DSSC with 20N–TiO₂ achieved a PCE of 6.16%, 20% higher than the control, attributed to increased dye uptake and reduced recombination.¹¹⁹

In conclusion, doping in TiO₂ significantly enhances its optoelectronic properties, leading to improved charge transfer, reduced recombination, and extended light absorption, making it a highly effective strategy to boost the performance and efficiency of TiO₂-based devices, particularly in DSSCs.

6.4.2. Surface passivation. Surface treatment of TiO_2 photoanodes is a key strategy for enhancing the efficiency and stability of DSSCs. TiO_2 , as the electron transport layer, faces challenges such as charge recombination, limited light absorption, and low electron mobility, which hinder overall performance. Surface treatments, including passivation, doping, and coating with advanced materials, help mitigate these issues by improving charge transport, reducing recombination, and extending light absorption into the visible spectrum. Techniques like $TiCl_4$ passivation and MXene coatings create barriers that reduce electron–hole recombination, boosting V_{OC} and J_{SC} .

Advanced nanomaterials, such as 2D-graphenes, MXenes, and plasmonic nanoparticles, enhance conductivity and light harvesting, leading to higher PCE. Additionally, these treatments improve DSSC stability by protecting ${\rm TiO_2}$ from degradation. Overall, surface-treated ${\rm TiO_2}$ photoanodes significantly enhance the photovoltaic performance and durability of DSSCs, making them crucial for advancing next-generation solar technologies. Recently, Tehare et~al. synthesized rutile ${\rm TiO_2}$ photoanodes in copper containers that were spin-coated with passivation layers (MgO, CaCO₃, ZrO₂, SnO₂). The MgO-passivated ${\rm TiO_2}$ electrode achieved the highest PCE of 6.05% and IPCE of 52%. Passivation increased electron lifetime from 0.48 ms to 0.65 ms and reduced charge transfer resistance from 36.9 Ω cm (pristine ${\rm TiO_2}$) to 20.16 Ω cm (MgO-passivated). The improvement is due to reduced charge recombination and

enhanced electron mobility, as the passivation layers, especially MgO, act as barriers that prevent recombination and improve charge transport. Additionally, optimized energy level alignment and surface morphology enhance light harvesting and charge injection, leading to higher efficiency.¹²⁰

In another report, Kumar et al. achieved a maximum photoconversion efficiency of 9.84% using o-phenylenediamine (aromatic amines)-capped TiO₂ composites as the scattering layer. The higher efficiency is attributed to the increased reflectivity of o-phenylenediamine-capped TiO2, which enhanced photon back-reflection to the photoanode, improving light absorption. Additionally, the carrier lifetime doubled from 4.29 ms (pristine TiO₂) to 9.8 ms, reducing charge recombination and contributing to improved efficiency.121 Further, Babu et al. studied RF-sputtered WO₃ for passivating TiO₂ to reduce electron loss from surface defects. The WO3-coated TiO2 maintained dye adsorption and enhanced the efficiency of DSSCs by approximately 10% compared to pristine TiO₂. This improvement is attributed to WO3 creating an energy barrier that promotes photo-electron injection while blocking reverse recombination. An optimal WO3 thickness was identified, as excessive coating reduced short-circuit current density by hindering electron injection. RF-sputtering proved effective for uniform, pinhole-free WO3 coatings, making it suitable for surface passivation in nanostructured photovoltaic devices. 122

Kaliamurthy et al. introduced a DSSC design with 10% SrF2 incorporated with a 90% TiO₂ photoanode. This configuration enhances charge separation and increases the dielectric constant ($\varepsilon' = 6.844 \times 10^6$), improving charge transport and collection efficiency by optimizing dye loading and reducing charge recombination. The electrostatic shielding of SrF₂ minimizes back electron transfer and passivates trap levels. As a result, the PCE improved to 7.58% compared to the reference DSSC, having a PCE of 6.99% under 1-sun illumination, reaching approximately 16.01% with an output power of 59.41 μW cm⁻² under 1000 lx LED-5000 K illumination. Rodrigues et al. explored the use of polymeric co-adsorbents, poly 4vinylbenzoic acid (PVBA) and poly(4-vinylpyridine) (P4VP), as alternatives to chenodeoxycholic acid (CDCA) in DSSCs. These polymers effectively suppress back electron transfer from the TiO₂/N719 photoanode to the I₃⁻/3I⁻ electrolyte, achieving 1sun equivalent PCEs of 8.3% (PVBA) and 9% (P4VP), with artificial light PCEs of 17.5% and 22%, respectively. PVBA's carboxylic groups enhance adsorption at the photoanode-electrolyte interface, leading to over 1000 hours of stable PCE performance, comparable to CDCA. Time-correlated single photon counting photoluminescence spectroscopy confirmed improved charge injection and excited dye lifetimes, while intrinsic device degradation was assessed using the ISOS-L2 protocol.124 Singh et al. used 1-D graphene nanoribbons (GNRs) in TiO2 compact and mesoporous layers to enhance quantum dot-sensitized solar cells (QDSSCs) and photoelectrochemical (PEC) water-splitting performance. The optimal GNR content achieved a maximum PCE of 2.33% in QDSSCs and a photocurrent density of 1.92 mA cm⁻² in PEC water splitting. Incorporating GNRs into the mesoporous layer further improved performance, resulting in a PCE of 3.06% for QDSSCs

and 2.39 mA cm⁻² for PEC water splitting. Overall, device optimization led to enhancements of 113% in PCE and 80% in photocurrent density, with co-sensitization yielding PCEs of 4.55% for QDSSCs and 2.67 mA cm⁻² for PEC water splitting, demonstrating the effectiveness of GNRs in improving charge transport and reducing recombination.125

Hence, passivation in TiO2-based DSSCs significantly enhances device performance by mitigating charge recombination and improving charge transport, thereby increasing PCE. Future research should focus on exploring novel passivating agents, such as hybrid materials or self-assembled monolayers, to further optimise the interface between the TiO₂ photoanode and the electrolyte. Additionally, integrating advanced characterization techniques can provide deeper insights into the mechanisms of passivation, enabling the development of more effective strategies for enhancing the stability and efficiency of DSSCs. Exploring environmentally friendly and cost-effective materials for passivation will also be crucial for the sustainable advancement of this technology.

6.4.3. Composite (hybrid) electrodes. DSSCs offer a promising solution for sustainable energy conversion, but their PCE remains a critical challenge. Recent studies have explored innovative strategies to enhance photoanodes and counter electrodes (CEs) performance by incorporating advanced nanocomposite materials. Lemos et al. 126 integrated Ti₃C₂T_r MXene with TiO2 to form hybrid photoanodes and demonstrated that adding 0.075 wt% Ti₃C₂T_x MXene flakes to TiO₂ led to a 20% enhancement in PCE, attributed to improved electron transport and prolonged electron lifetimes. Density functional theory (DFT) calculations confirmed that the Ti₃C₂T_x MXene-TiO₂ interface lowers the anatase conduction band potential, facilitating more efficient electron migration from the N719 dye to the output terminal. Additionally, better photocarrier separation was observed, further supporting the enhanced device performance. Later, Nagalingam et al. 127 employed polyaniline (PANI)-modified $Ti_3C_2T_x$ composites (PANI- $Ti_3C_2T_x$) as CEs in DSSCs. The incorporation of PANI improved the electrical conductivity and surface wettability of Ti₃C₂T_x, leading to increased electroactive sites and faster ion transport. Electrochemical analysis revealed that the PANI-Ti₃C₂T_r-CE exhibited superior electrocatalytic activity and comparable charge transfer resistance to platinum, with a PCE of 6.9% under simulated sunlight. Notably, the PANI-Ti₃C₂T_x-CE demonstrated exceptional stability and reproducibility, highlighting its potential as a cost-effective alternative to platinum-based electrodes.

Another study by Yan et al. 128 focused on the co-introduction of Nb₂O₅ and Ti₃C₂ quantum dots (MQDs) into the photoanode. This combination significantly altered the energy level alignment, resulting in enhanced light absorption, improved carrier separation, and accelerated charge transfer. The DSSC fabricated with the Nb₂O₅-Ti₃C₂ MQD composite photoanode achieved a remarkable PCE of 7.24%, substantially higher than the standard device's efficiency of 4.60%. Nagalingam et al. 129 again presented a poly(3,4-ethylene dioxythiophene)-decorated MXene (PEDOT@Ti₃C₂T_x) composite as a cost-effective alternative to Pt-CEs in DSSCs. The 2D Ti₃C₂T_x MXene was synthesized via selective chemical etching, followed by the electro-

polymerization of EDOT monomers. Under AM 1.5G illumination, the PEDOT@Ti₃C₂T_x-CE achieved a PCE of 7.12%, compared to 8.7% for Pt-CE, outperforming PEDOT-only and Ti₃C₂T_r-only CEs. The composite demonstrated enhanced charge transfer and mass transport capabilities. Stability tests over 15 days showed excellent performance retention and corrosion resistance, establishing PEDOT@Ti₃C₂T_r as a viable, scalable alternative to Pt for DSSC applications.

Lastly, a Ti₃C₂T_x-polythiophene (Ti₃C₂T_x-PTh) composite fabricated via interfacial polymerization demonstrated its effectiveness as a CE in DSSCs. Structural and electrochemical characterization revealed that the composite exhibited superior electrocatalytic activity and reduced charge transfer resistance compared to individual components. The DSSC using the Ti₃C₂T_r-PTh CE achieved a PCE of 5.83%, comparable to that of traditional platinum-based CEs. 130 These findings underscore the potential of Ti₃C₂T_x-based composites to replace conventional platinum electrodes, offering a more sustainable and cost-effective solution for next-generation DSSCs. In summary, the comparative analysis of these studies highlights the versatility of Ti₃C₂T_x MXene in enhancing the performance of DSSCs through various modifications. The incorporation of conductive polymers like PANI and PTh, as well as the introduction of Nb₂O₅ and MQDs, significantly improves charge transport, carrier separation, and catalytic activity. These advancements position Ti₃C₂T_r/TiO₂-based composites as a promising alternative to traditional materials, paving the way for the development of high-efficiency, low-cost DSSCs with enhanced stability and scalability.

Charge transport and electronic analogy

1-D TiO₂ nanostructures have distinct advantages over bulk TiO2 with a wide bandgap, including increased surface area, a large number of active sites, and the impact of quantum confinement phenomena. The main determinants of their electrical characteristics are the size, unique crystal facets, shape, and synchronization of these nanostructures, as well as their alignment. Quantum confinement factors cause the bandgap to widen when nanowire size approaches the nanoscale regime. Doping with foreign elements is the main tactic used to adjust the bandgap and realign the valence and conduction band configurations favourably with the sensitizer energy levels. With the use of this method, one can tune their electrical characteristics precisely, improving their functionality for use in DSSC. Vertically arranged nanowire-based photoanodes have been used to provide the most outstanding DSSC performances. In nanorods, a large decrease in the grain boundaries, which frequently serve as electron traps, results in a boost in the electron diffusion length and, as a result, better charge transfer. TNRs aspect ratio can be changed in order to change the bandgap. The conduction band edge shifts downward as the aspect ratio of nanorods rises. Similar to this, adding surface roughness and meso-porosity can increase the surface area of nanorods, further boosting their performance in DSSCs. These techniques are essential for enhancing the electrical characteristics and effectiveness of photoanodes based on

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 13 February 2025. Downloaded on 11/4/2025 6:25:21 AM.

Review

nanorods for cutting-edge solar cell applications. Quantum confinement effects, an exciting phenomenon only seen in hydrothermal tubes, are shown in TNTs with a wall thickness below 5 nm. The abundance of oxygen vacancies and Ti³⁺ ions is another element enhancing charge transmission in these nanotubes. The potential of these nanotubes to transfer charges is significantly influenced by the annealing temperature. Numerous techniques, such as doping, surface adsorption, the creation of heterojunctions, and surface embellishment, can be used to design the bandgap in nanotubes. With the help of these techniques, the bandgap of the nanotubes may be precisely altered, affecting its electrical characteristics and, as a result, improving their efficiency in future applications, such as DSSC.85,131-135

Despite ongoing debates on the exact mechanisms of photovoltaic action and the performance limitations of the original DSSC, there is consensus on the fundamental charge separation process upon illumination. This process involves the photoexcitation of the dye, the rapid injection of the excited electron into the TiO₂ (on a timescale of <10⁻¹² s), and the regeneration of the dye via electron transfer from the I⁻/I₃⁻ redox couple, which occurs within 10 ns. 136-139 The energy-band diagram of the electrolyte DSSC is well understood in thermal equilibrium despite the complex nanoscale mixture of TiO2 and electrolyte. The TiO2 network is idealized as columns (10-15 nm in diameter) on an FTO substrate or a TiO2 blocking layer, as

shown in Fig. 18(a). Due to moderate doping, the charge within individual TiO₂ particles is too small to cause significant band bending.140 The Helmholtz layer of the electrolyte screens any charge, preventing a substantial electric field along the TiO₂ columns, as shown in the band diagram for the conduction and valence bands in Fig. 18(b).

At the TiO2-electrolyte interface, the equilibrium Fermi level $(E_{\rm F})$ is governed by the redox energy $(E_{\rm redox})$ of the electrolyte, which defines the potential at the interface.141 This is because the TiO₂ is in contact with the electrolyte, and the Fermi level of TiO₂ aligns with the redox potential of the electrolyte under equilibrium conditions. Additionally, an interface dipole forms at the TiO2-electrolyte interface due to several factors, including the polarity of the adsorbed dye, the Helmholtz layer of the electrolyte, and the differential adsorption of ions. Specifically, Li⁺ cations are adsorbed closer to the interface than I⁻ anions. 142,143 This ion distribution results in a potential difference (V_{if}) at the interface. This potential drop, V_{if} , leads to the downward shift of the conduction band energy (E_{CB}) of TiO_2 relative to the E_{redox} of the electrolyte, creating a barrier that affects the charge transfer process. The energy alignment shown in Fig. 18(b), with the vacuum level ($E_{\rm vac}$), illustrates the influence of the dipole and potential drop at the interface, which plays a key role in determining the efficiency of charge separation and transport in DSSCs. An additional voltage drop, V_{bi}, is required at the TiO₂-SnO₂/F interface to align the Fermi

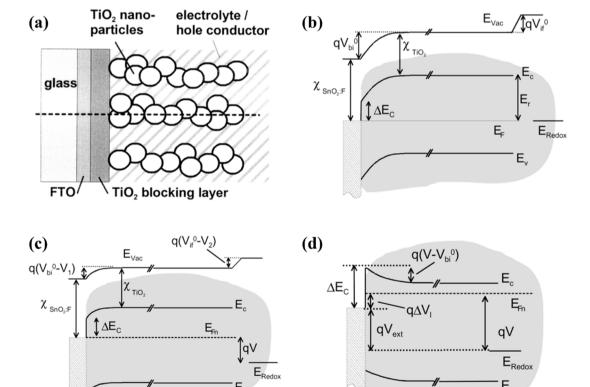


Fig. 18 (a) Schematic side view of a DSSC comprising nanocrystalline 1-D TiO₂ photoanodes and electrolyte, (b and c) schematic band model of DSSC under dark and light conditions, where the interfacial band bending arises due to the negative charges present in the electrolyte, and (d) detailed band diagram where light-induced V exceeds the $V_{\rm bi}$.

levels between the TiO2 and SnO2/F layers, ensuring proper energy level alignment, which is given below:

$$qV_{\rm bi} = E_{\rm vac} - E_{\rm redox} - \chi_{\rm SnO_2} - qV_{\rm if} \tag{11}$$

where the electron affinity (χ_{SnO_2}) of the SnO_2/F plays a significant role in determining the position of the Fermi energy at the TiO_2 -SnO₂/F interface In DSSCs, the built-in voltage (V_{bi}) at the TiO2-SnO2/F interface is influenced by the charge distribution between the electrolyte and the highly doped SnO₂/F layer.¹⁴⁴ Negative charges from the electrolyte penetrate the TiO₂ network, while positive charges from ionized SnO₂/F atoms are confined to a thin layer near the TiO2 interface. This creates a potential drop (V_{if}) across the TiO₂-electrolyte interface, which is limited to the first one or two TiO2 nanograins due to the charge distribution geometry. The built-in voltage primarily affects the electron dynamics in these initial layers, with estimates of $V_{\rm bi}$ ranging from 0.3 V to 0.7 V, depending on material configuration and doping levels. 145,146

The magnitude and significance of the $V_{\rm bi}$ in DSSCs remain subjects of debate. It is crucial to distinguish this from the separate question of whether DSSCs can be analyzed similarly to classical p-n-junction solar cells. Applying Shockley's p-njunction theory can be useful for understanding DSSC behaviour, both in electrolyte-based and hole-conductor-based systems. However, experimental evidence does not suggest that the $V_{\rm bi}$ necessarily limits the $V_{\rm OC}$ of DSSCs, just as it does not strictly constrain p-n-junction solar cells.

Upon illumination, photoelectrons from the dye are injected into TiO₂, causing a split in the Fermi level between TiO₂ and the electrolyte, which drives the primary photovoltaic action in DSSCs. For external photovoltage measurement, the excess electrons in TiO₂ must connect to the SnO₂/F front electrode, while the redox potential of the redox couple must interface with the Pt back electrode. At open-circuit conditions, the photogenerated current density (j_{ph}) , balances the recombination current density (j_r) . Due to the extensive interface area between TiO_2 and the electrolyte or hole conductor (HC), recombination mainly occurs at the TiO₂ interface, involving oxidized redox species or, for solid-state DSSCs, holes from the HOMO. Cahen et al.141 identified the $V_{\rm OC}$, with the chemical potential difference, $\Delta\mu$, under these conditions, where $j_{\rm r}=j_{\rm ph}$, highlighting the role of interfacial recombination in determining $V_{\rm OC}$. Based on Gerischer's semiconductor-electrolyte electron transfer theory, a general expression for the $V_{\rm OC}$ was formulated. This expression relates $V_{\rm OC}$ to the interfacial electron dynamics, encompassing the balance between the photogenerated electron density in the semiconductor and the redox energy level of the electrolyte, thereby providing insights into the voltage generation mechanism within DSSCs and given as,

$$V_{\text{OC}} = \frac{kT}{q} \ln \left\{ \frac{j_{\text{ph}}}{q\nu(E_{\text{CB}}) \left(\frac{kT}{4\pi\lambda}\right)^{1/2} N_{\text{CB}} c_{\text{ox}}} \right\} + \frac{E_{\text{CB}} - E_{\text{redox}}}{q} + \frac{\left(E_{\text{CB}} - E^0 - \lambda\right)^2}{4\lambda a}$$

$$(12)$$

where $N_{\rm CB}$ is the effective density of states in TiO_{2(CB)}, while $c_{\rm ox}$ denotes the concentration of oxidized species in the electrolyte. The term $\nu(E_{\rm CB})$ describes the frequency factor for electron transfer from the semiconductor to the electrolyte at the conduction band edge energy. Additionally, E^0 represents the standard redox potential as per Nernst's equation, and λ indicates the solvation reorganization energy. The derived expressions for $V_{\rm OC}$ assume that the excess charge carriers at the TiO₂electrolyte interface are governed by the externally applied voltage, whether this voltage drops across a space-charge region within TiO2 or across the SnO2/F-TiO2 interface. Furthermore, for solid-state DSSCs, $V_{\rm OC}$ is constrained by the recombination of photogenerated electrons in TiO2 with holes in the HC, as given:

$$V_{\rm OC} = \frac{kT}{q} \ln \left\{ \frac{j_{\rm ph}}{qSN_{\rm CB}} \right\} + \frac{E_{\rm CB} - E_{\rm F}}{q} \tag{13}$$

where *S* is interfacial recombination velocity.

When an external voltage drop occurs over the device, the effective band diagram must be adjusted from Fig. 18(b and c). This modifies the initial potential barriers $V_{\rm bi}$ and $V_{\rm if}$, with the externally measured or applied voltage V being the sum of V_1 and V_2 . Consequently, this external voltage reduces one or both of these potential barriers according to,

$$V_{\rm bi} + V_{\rm if} = V_{\rm bi}^{V=0} - V_1 + V_{\rm if}^{V=0} - V_2 = V_{\rm bi}^0 + V_{\rm if}^0 - V$$
 (14)

At zero applied voltage, the built-in voltage $V_{\mathrm{bi}}^{\ V=0}$ and the interfacial potential $V_{\rm if}^{V=0}$ remain at their initial values. When an external voltage is applied, $V_{\rm bi}$ decreases similarly to how the built-in potential of a bulk p-n-junction diode reduces under bias. However, the reduction of V_{if} is unique to DSSC and has no equivalent in conventional p-n-junction devices.

Zaban and co-workers noted that if the external voltage V only drops across the TiO_2 -electrolyte interface, reducing $V_{if}^{V=0}$ by $V = V_2$ and $V_1 = 0$, it would create an internal barrier, impeding electron injection into the TiO2 or dye regeneration from the electrolyte, or both. ¹⁴² If V solely influences the $V_{\rm bi}$, the scenario where V exceeds $V_{\rm bi}^{V=0}$ raises concerns. Photoelectrons in TiO2 would then need to overcome a potential barrier between the TiO2 and the SnO2/F window layer, which, while not necessarily affecting the open-circuit voltage $V_{\rm OC}$, could induce resistive losses, reducing the fill factor. Simulations by Ferber and Luther showed that even a low built-in voltage of 0.48 V could yield a V_{OC} around 0.78 V. This is consistent with theoretical constraints, as $V_{\rm OC}$ is limited by $V_{\rm OC} < V_{\rm bi}^{V=0} + \Delta E_{\rm CB}$, where $\Delta E_{\rm CB} = \chi_{\rm SnO_2} - \chi_{\rm TiO_2}$. Nonetheless, the fill factor declines as $V_{\mathrm{bi}}^{V=0}$ decreases from 0.66 to 0.48 V due to a loss-voltage ΔV_{I} , which is necessary to push electrons over the electrostatic barrier $(V - V_{bi}^{V=0})$ into SnO₂/F (Fig. 18(d)). Consequently, the usable external voltage $V_{\rm ext} = V - \Delta V_{\rm I}$, with $\Delta V_{\rm I}$ being currentdependent and vanishing at $V_{\text{ext}} = V = V_{\text{OC}}$.

The transport of electrons within the TiO₂ network of DSSCs is governed by diffusion rather than drift, due to the absence of a significant electric field throughout most of the TiO2 structure. Under illumination or forward bias conditions ($V < V_{OC}$), electron movement from the TiO2 nanoparticles to the front Review RSC Advances

electrode primarily occurs through a diffusion-driven process. At moderate forward bias, the overall admittance of the DSSC is primarily influenced by the diffusion admittance of electrons in ${\rm TiO_2}$. According to the classical theory for single-sided p-n junctions described by Shockley, the time-dependent diffusion equation yields a complex expression for the diffusion admittance $(Y_{\rm diff})$ of minority carriers, particularly for voltages exceeding 3kT/q. ¹⁵⁰

$$Y_{\text{diff}} = \frac{q n_{\text{j}} D_{\text{e}}}{L_{\text{D}_{e}}^{*}} \frac{q}{kT} \tanh \frac{d_{\text{T}}}{L_{\text{D}_{e}}^{*}}$$
(15)

here, $D_{\rm e}$ represents the diffusion constant, while $n_{\rm j}$ denotes the excess electron density, defined as $n_{\rm j}=n_{\rm 0}(\exp(qV/(kT))-1)$, where $n_{\rm 0}$ is the equilibrium electron density. The effective diffusion length, $L_{\rm De}$, is expressed as a complex quantity, $L_{\rm De}(1+i\omega\tau)^{-1/2}$, which depends on the angular frequency $\omega=2\pi f$. Importantly, this formulation neglects electron recombination at the terminal of the TiO₂ column with length $d_{\rm T}$.

The band model depicted in Fig. 18(b and c) applies to DSSCs with a liquid electrolyte. For solid-state DSSCs, two key distinctions must be addressed. Firstly, the Fermi energy level of the organic hole conductor differs from the redox potential of the I^-/I_3^- redox couple, with an energy difference of $E_{\rm vac} - E_{\rm redox} = -4.95$ eV.¹⁵¹ Secondly, in solid-state cells, the Fermi energy is influenced by the effective density of states in the valence band ($N_{\rm V}$), and the doping density as mentioned below:

$$E_{\rm F} = E_{\rm HOMO} + kT \ln \left(\frac{N_{\rm V}}{N_{\rm A}} \right) \tag{16}$$

Using values of $N_{\rm V}\approx 10^{21}~{\rm cm}^{-3}$ and $N_{\rm A}\approx 10^{17}~{\rm cm}^{-3}$, the $E_{\rm F}$ of the HC layer is calculated to be 0.24 eV above the HOMO energy ($E_{\rm HOMO}$). The HOMO energy, measured via cyclic voltammetry, is approximately $E_{\rm HOMO}-E_{\rm vac}=-4.8$ eV in solution. Although the solid-state value may vary slightly, this estimation suggests a 0.2 eV difference between $E_{\rm HOMO}$ in the solid-state cell and the redox energy in the electrolyte-based cell. Another significant difference between solid-state and electrolyte DSSCs is the lower charge carrier density of the HC, compared to the high ion density in the redox electrolyte, resulting in a wider space charge region instead of a thin Helmholtz layer. ¹⁵²

7. Importance of 1-D TiO₂ nanorods

Notably in the area of photovoltaics industry, 1-D TiO₂ photoanodes are essential for energy conversion. They are important for a number of reasons.

7.1 Increased light absorption

Unlike to conventional ${\rm TiO_2}$ thin films, 1-D ${\rm TiO_2}$ nanostructures, such as nanowires, nanotubes, nanobelts or nanoneedles, offer an enormously huge surface area-to-volume ratio. This feature makes it feasible to use sunlight more effectively, improving the device's overall ability to convert photo energy into electrical energy. ^{153–155}

7.2 Superior charge transport

For photogenerated electrons and holes, 1-D ${\rm TiO_2}$ structures offer effective charge transport channels. Longer carrier lifetimes and larger photocurrents are produced as a consequence of the dearth of defects and grain boundaries in these structures. Higher energy conversion efficiencies are a result of this enhanced charge transport. ^{156–158}

7.3 Tunability of the bandgap

The 1-D structures' size and shape can be changed by doping *etc.* to alter the bandgap of TiO₂. The bandgap can be tuned for better alignment with the solar spectrum and more effective solar energy harvesting.^{159,160}

7.4 Stability and durability

1-D TiO₂ structures display outstanding chemical stability and photo-corrosion resistance. This characteristic makes the photoanodes excellent for long-term energy conversion applications since it guarantees that they can endure repeated exposure to adverse weather conditions.^{161–163}

7.5 Flexibility

1-D TiO₂ structures are readily incorporated into a wide range of device topologies, including DSSCs, perovskite solar cells, and quantum dot solar cells. They are adaptable components in energy conversion systems because of their compatibility with various materials and fabrication processes.^{22,164}

Moreover, other than application in photovoltaics, 1-D TiO_2 nanostructures like nanotubes, nanowires, nanobelts, and nanorods, have been regarded as highly desirable candidates for a number of uses, including the photocatalytic degradation of pollutants, the photocatalytic conversion of CO_2 into energy fuels, water splitting, supercapacitors, and lithium-ion batteries. Therefore, the remarkable properties of 1-D TiO_2 nanostructures, ranging from enhanced light absorption and charge transport to tunability of bandgap and exceptional stability, position them as versatile and vital components not only in photovoltaics but also in a wide array of sustainable energy and environmental applications, showcasing their potential to drive advancements in renewable energy and catalysis technologies.

8. Current limitations and future perspective

DSSCs face critical challenges related to the electrolyte, Pt-counter electrode, and overall stability. The conventional $\rm I^-/I_3^-$ electrolyte suffers from volatility, leakage, and corrosiveness, leading to degradation of cell components and limiting long-term stability. Its narrow electrochemical window constrains the $V_{\rm OC}$, while slow redox species diffusion reduces the FF and overall efficiency. The high cost and scarcity of Pt, commonly used for its superior catalytic activity, significantly increase the production cost of DSSCs. Additionally, Pt degrades under exposure to the corrosive electrolyte, further impacting

device longevity. These limitations have prompted research into cost-effective alternatives, such as carbon-based materials and transition metal compounds. 165,166

Stability is another major concern, with TiO2 photoanodes susceptible to UV-induced degradation and dyes prone to photodegradation and thermal instability. The electrolyte also faces evaporation and leakage issues, reducing ionic conductivity over time. Effective encapsulation strategies are essential but challenging to implement without increasing costs. Current efforts to address these limitations include the development of solid-state electrolytes, alternative catalysts, and surface passivation techniques to enhance durability and efficiency, making DSSCs a more viable option for sustainable energy applications. 167-170 Future evolutions in 1-D TiO2 nanostructures have enormous potential to influence the development of sustainable and energy-conversion technologies. Even more significant advancements in this area are probably possible with continued research and invention. These nanostructures might be crucial in solving crucial energy challenges.

8.1 Enhanced efficiency

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 13 February 2025. Downloaded on 11/4/2025 6:25:21 AM.

We anticipate being able to precisely build 1-D TiO₂ structures with respect to their attributes as our knowledge of nanoscale processes expands. This might lead to even better energy conversion efficiency, overcoming present constraints and boosting the affordability of renewable energy sources. Future approaches include integrating heterostructures and cocatalysts to improve charge separation, doping to extend light absorption, and surface engineering to minimize defect states. Scalable synthesis methods and AI-driven material optimization can further address challenges like recombination losses and cost barriers, positioning 1-D TiO2 as a key material for efficient and affordable renewable energy solutions.

8.2 Multifunctionality

Future research may unlock novel functionalities of 1-D TiO₂ nano-structures, enabling them to serve as dual-purpose platforms for energy conversion and sensing. These advancements could facilitate their integration into smart energy grids for efficient energy management while also enabling real-time monitoring of environmental parameters such as pollutants, temperature, and humidity. By leveraging their photocatalytic and electronic properties, 1-D TiO₂ structures could be tailored for applications in self-powered sensors, wearable devices, and Internet of Things (IoT) systems. Such multifunctionality would significantly broaden their impact across energy, environmental, and industrial sectors.

8.3 Integration and hybridization

Collaborative efforts to combine 1-D TiO₂ nanostructures with advanced materials like perovskites, quantum dots, or MXenes could unlock synergistic effects, enhancing energy capture, transfer, and storage. By leveraging the unique properties of each material, such as the excellent charge transport of TiO₂ and the superior light-harvesting capabilities of perovskites or quantum dots, these hybrid systems can achieve enhanced

efficiency and flexibility. This integration may pave the way for innovative applications in next-generation solar cells, energy storage devices, and adaptable energy platforms for diverse environments.

8.4 Beyond photovoltaics

The versatility of 1-D TiO2 nanostructures could extend their application beyond photovoltaics into industries such as thermoelectrics. Their unique properties, including high surface area and tunable electronic characteristics, could be harnessed to efficiently convert waste heat into electricity, thereby improving energy efficiency. By integrating 1-D TiO2 nanostructures into thermoelectric devices, it may be possible to develop sustainable solutions for harnessing waste heat in industrial processes, transportation, and consumer electronics, contributing to energy conservation and reducing overall environmental impact.

8.5 Energy storage revolution

Integrating 1-D TiO₂ nanostructures into energy storage systems, such as lithium-ion batteries and supercapacitors, can revolutionize energy storage technologies. These structures could significantly enhance the performance of these systems by improving charge storage capacity, increasing charge/ discharge rates, and extending lifespan. The unique properties of 1-D TiO2, including high conductivity and stability, could enable faster charging times and more efficient energy retention. Moreover, their incorporation could improve the safety and reliability of energy storage devices, making them more suitable for a wide range of applications, from portable electronics to electric vehicles, while contributing to the overall advancement of sustainable energy solutions.

8.6 CO₂ utilisation and catalysis

In the context of sustainable chemistry, 1-D TiO2 nanostructures hold significant potential as catalysts for the conversion of CO2 into valuable fuels or chemicals. Their photocatalytic properties could enable efficient solar-driven CO2 reduction processes, helping to mitigate greenhouse gas emissions while simultaneously producing useful by-products. By optimizing their surface properties and enhancing charge carrier dynamics, 1-D TiO2 could play a key role in advancing carbon-neutral technologies, contributing to the transition towards a society with minimal carbon emissions and a more sustainable approach to energy production and resource utilization.

8.7 Large-scale manufacturing

For 1-D TiO₂ nanostructures to achieve widespread adoption, scaling up their production is crucial. The economic feasibility of these technologies will largely depend on the development of scalable, cost-effective manufacturing processes. Innovations in fabrication methods, such as continuous-flow synthesis, roll-toroll processing, or green chemistry approaches, could enable large-scale production while maintaining the desired material

Review **RSC Advances**

properties. Additionally, reducing the cost of raw materials and energy-intensive steps will be key to making these advanced nanostructures accessible for commercial applications in energy, environmental, and industrial sectors, thereby accelerating their integration into sustainable technologies.

8.8 Global sustainability

Deploying 1-D TiO2 nanostructures in underdeveloped countries could provide sustainable and clean energy solutions in regions with limited or unreliable conventional energy infrastructure. These nanostructures could enable the creation of affordable, efficient energy systems, such as solar cells and energy storage devices, which are crucial for reducing dependence on fossil fuels and improving energy access. By facilitating the transition to renewable energy, 1-D TiO2 nanostructures could contribute to global sustainability efforts, ensuring equitable access to energy for all while also supporting the fight against climate change and fostering economic development in underserved communities.

Fundamentally, 1-D TiO₂ nanostructures have a bright future in energy conversion and sustainable technology. These structures have the potential to alter our energy environment and usher in a more sustainable and resilient future as interdisciplinary collaborations bloom and as our understanding of nanomaterials advances.

9. Conclusion

This review provides an in-depth exploration of 1-D TiO₂nanostructured photoanode materials used in DSSCs, examining the intricate designs and operational principles of various 1-D TiO₂ nanostructures. The shift towards renewable energy becomes increasingly critical as the world continues to rely heavily on non-renewable energy sources, leading to significant environmental damage and resource depletion. Solar energy, in particular, stands out as an abundant and sustainable source, offering the potential for both electricity and hydrogen fuel production. DSSCs, as efficient energy converters, are emerging as a promising solution to address the global energy crisis. Recent advancements in 1-D TiO2 nanostructures, such as nanoparticles, nanowires, nanorods, and nanotubes, have made them ideal candidates for high-performance DSSC photoanodes, owing to their superior light-scattering properties and rapid electron transport capabilities. Overcoming surface area limitations holds promise for even greater efficiency, positioning 1-D TiO2 as a more attractive option than other semiconductors due to its well-matched band structure with the sensitizer and efficient charge transport. Furthermore, 1-D TiO2's non-toxic nature and robust functionality enhance its appeal in sustainable energy applications.

Future research may focus on extending the absorption spectrum of 1-D TiO₂ into the infrared (IR) region to further enhance charge collection and broaden its applicability under diverse lighting conditions. The integration of 1-D TiO2 with other advanced materials, such as perovskites, quantum dots, and MXenes, could enable synergies that maximize energy

capture, transfer, and storage. Additionally, the exploration of 1-D TiO₂ nanostructures in energy storage systems, CO₂ conversion technologies, and underdeveloped regions could further contribute to a sustainable global energy transition. By overcoming current challenges in scalability, surface engineering, and hybridization, 1-D TiO2-based DSSCs can play a pivotal role in the future of clean energy solutions, advancing both energy efficiency and environmental sustainability.

Data availability

All data used will be made available by the corresponding author on reasonable request.

Author contributions

Kumar Vaisno Srivastava: conceptualization, visualization, validation, investigation, methodology, formal analysis, writing - original draft, writing - review & editing, and resources. Pooja Srivastava: writing - review & editing. Akancha Srivastava: formal analysis. Raj Kumar Maurya: supervision. Yatendra Pal Singh: supervision. Abhishek Srivastava: conceptualization, visualization, validation, investigation, methodology, formal analysis, writing - original draft, writing - review & editing, resources, supervision.

Conflicts of interest

There is no conflict to declare.

Acknowledgements

KVS, YPS, and RKM acknowledge the Department of Physics, Mangalayatan University, and the Department of Physics, RML University Faizabad, for providing laboratory support and guidance. All authors are thankful to Prof. Ravikant, Dean of Research and Development, Mangalayatan University.

References

- 1 F. Pietro Colelli, J. Emmerling, G. Marangoni, M. N. Mistry and E. De Cian, Nat. Commun., 2022, 13, 1-12.
- 2 L.-E. British Oil and BP Gas Company, Statistical Review of World Energy, 2017.
- 3 M. Green, E. Dunlop, J. Hohl-Ebinger, M. Yoshita, N. Kopidakis and X. Hao, Prog. Photovoltaics Res. Appl., 2021, 29, 3-15.
- 4 M. Grätzel, J. Photochem. Photobiol. C Photochem. Rev., 2003, 4, 145-153.
- 5 M. Freitag, J. Teuscher, Y. Saygili, X. Zhang, F. Giordano, P. Liska, J. Hua, S. M. Zakeeruddin, J. E. Moser, M. Grätzel and A. Hagfeldt, Nat. Photonics, 2017, 11, 372-378.
- 6 B. O'Regan, M. Grätzel, et al., Nature, 1991, 354, 737-740.
- 7 K. Kakiage, Y. Aoyama, T. Yano, K. Oya, J. I. Fujisawa and M. Hanaya, Chem. Commun., 2015, 51, 15894-15897.

- 8 S. N. Tamilselvan and S. Shanmugan, Clean Energy, 2024, 8, 238-257.
- 9 Z. Tang, J. Wu, M. Zheng, J. Huo and Z. Lan, Nano Energy, 2013, 2, 622-627.
- 10 E. Garnett, L. Mai and P. Yang, Chem. Rev., 2019, 119, 8955-8957.
- 11 M. Nehra, N. Dilbaghi, G. Marrazza, A. Kaushik, R. Abolhassani, Y. K. Mishra, K. H. Kim and S. Kumar, Nano Energy, 2020, 76, 104991.
- 12 H. J. Yun, H. Lee, J. B. Joo, W. Kim and J. Yi, J. Phys. Chem. C, 2009, 113, 3050-3055.
- 13 A. Razzaq, T. G. Allen, W. Liu, Z. Liu and S. De Wolf, Joule, 2022, 6, 514-542.
- 14 X. Li, Y. Yang, S. Huang, K. Jiang, Z. Li, W. Zhao, J. Yu, O. Gao, A. Han, J. Shi, J. Du, F. Meng, L. Zhang, Z. Liu and W. Liu, Sol. Energy Mater. Sol. Cells, 2022, 247, 111951.
- 15 C. Becker, D. Amkreutz, T. Sontheimer, V. Preidel, D. Lockau, J. Haschke, L. Jogschies, C. Klimm, J. J. Merkel, P. Plocica, S. Steffens and B. Rech, Sol. Energy Mater. Sol. Cells, 2013, 119, 112-123.
- 16 T. D. Lee and A. U. Ebong, Renew. Sustain. Energy Rev., 2017, 70, 1286-1297.
- 17 S. Ilic and V. Paunovic, Facta Univ. Ser. Electron. Energ., 2019, 32, 91-104.
- 18 H. Tributsch, Coord. Chem. Rev., 2004, 248, 1511-1530.
- 19 A. Zatirostami, J. Alloys Compd., 2020, 844, 156151.
- 20 A. S. H. Luque, Handbook of Photovoltaic Science and Engineering, 2011.
- 21 V. Sugathan, E. John and K. Sudhakar, Renew. Sustain. Energy Rev., 2015, 52, 54-64.
- 22 K. Sharma, V. Sharma and S. S. Sharma, Nanoscale Res. Lett., 2018, 13, 1-46.
- 23 R. Katoh and A. Furube, J. Photochem. Photobiol. C Photochem. Rev., 2014, 20, 1-16.
- 24 J. A. Anta, I. Mora-Seró, T. Dittrich and J. Bisquert, J. Phys. Chem. C, 2007, 111, 13997-14000.
- 25 N. C. Deb Nath and J. J. Lee, J. Ind. Eng., 2019, 78, 53-65.
- 26 A. J. Frank, N. Kopidakis and J. Van De Lagemaat, Coord. Chem. Rev., 2004, 248, 1165-1179.
- 27 M. G. Uddin, Development of Simplified In Situ Processing Routes for Rear-Side Patterning of Silicon Heterojunction Interdigitated Back Contact (SHJ-IBC) Solar Cells, M.Sc. thesis, University of Eastern Finland, 2018, p. 90.
- 28 K. Zhu, N. Kopidakis, N. R. Neale, J. Van De Lagemaat and A. J. Frank, J. Phys. Chem. B, 2006, 110, 25174-25180.
- 29 F. De Angelis, S. Fantacci and A. Selloni, Nanotechnology, 2008, 19, 42.
- 30 K. Zhu, N. R. Neale, A. Miedaner and A. J. Frank, Nano Lett., 2007, 7, 69-74.
- 31 J. K. W. Kumari, N. Sanjeevadharshini, M. A. K. L. Dissanayake, G. K. R. Senadeera and C. A. Thotawatthage, Ceylon J. Sci., 2016, 45, 33.
- 32 P. Wang, S. M. Zakeeruddin, R. Humphry-Baker, J. E. Moser and M. Grätzel, Adv. Mater., 2003, 15, 2101-2104.
- 33 P. J. Cameron and L. M. Peter, J. Phys. Chem. B, 2003, 107, 14394-14400.

- 34 J. Van De Lagemaat, N. Kopidakis, N. R. Neale and A. J. Frank, Phys. Rev. B - Condens. Matter Mater. Phys., 2005, 71, 1-7.
- 35 S. Pace, A. Resmini, I. G. Tredici, A. Soffientini, X. Li, S. Dunn, J. Briscoe and U. Anselmi-Tamburini, RSC Adv., 2018, 8, 9775-9782.
- 36 M. G. Ju, M. Chen, Y. Zhou, H. F. Garces, J. Dai, L. Ma, N. P. Padture and X. C. Zeng, ACS Energy Lett., 2018, 3, 297 - 304
- 37 X. Yu and W. Zeng, J. Mater. Sci. Mater. Electron., 2016, 27, 7448-7453.
- 38 N. Prabavathy, S. Shalini, R. Balasundaraprabhu, Velauthapillai, S. Prasanna, P. Walke N. Muthukumarasamy, J. Mater. Sci. Mater. Electron., 2017, 28, 9882-9892.
- 39 S. Corby, R. R. Rao, L. Steier and J. R. Durrant, Nat. Rev. Mater., 2021, 6, 1136-1155.
- 40 M. B. Tahir, M. Rafique, M. S. Rafique, N. Fatima and Metal Oxide- and Metal Sulfide-Based Nanomaterials as Photocatalysts, Elsevier Inc., 2020.
- 41 C. P. Lee, C. T. Li and K. C. Ho, Mater. Today, 2017, 20, 267-
- 42 A. P. K. B. Bhojanaa, A. Soundarya Mary, K. S. Shalini Devi and N. Pavithra, Sol. RRL, 2022, 6, 2100792.
- 43 N. Baig, I. Kammakakam, W. Falath and I. Kammakakam, Mater. Adv., 2021, 2, 1821-1871.
- 44 F. W. Low and C. W. Lai, Renew. Sustain. Energy Rev., 2018, 82. 103-125.
- 45 A. Al, R. Mashfiqua, D. Datta, S. Ghosh, O. Datta, A. Molla and M. E. Begum, Heliyon, 2024, 10, e40776.
- 46 Z. Yang, Z. Ma, J. Ren, Y. Xiong and F. Ren, Opt. Mater., 2024, 116521.
- 47 H. Cui, H. Liu, J. Shi and C. Wang, Int. J. Photoenergy, 2013, DOI: 10.1155/2013/364802.
- 48 W. Zhao, P. Guo, J. Wu, D. Lin, N. Jia, Z. Fang, C. Liu, Q. Ye, J. Zou, Y. Zhou and H. Wang, Nano-Micro Lett., 2024, 16, 1-14.
- 49 C. Zhen, T. Wu, R. Chen, L. Wang, G. Liu and H. M. Cheng, ACS Sustain. Chem. Eng., 2019, 7, 4586-4618.
- 50 Y. S. Kim, H. J. Jin, H. R. Jung, J. Kim, B. P. Nguyen, J. Kim and W. Jo, Sci. Rep., 2021, 11, 1-10.
- 51 K. Bourikas, C. Kordulis and A. Lycourghiotis, Chem. Rev., 2014, 114, 9754-9823.
- 52 D. O. Scanlon, C. W. Dunnill, J. Buckeridge, S. A. Shevlin, A. J. Logsdail, S. M. Woodley, C. R. A. Catlow, M. J. Powell, R. G. Palgrave, I. P. Parkin, G. W. Watson, T. W. Keal, P. Sherwood, A. Walsh and A. A. Sokol, Nat. Mater., 2013, 12, 798-801.
- 53 S. A. Kim, S. K. Hussain, M. A. Abbas and J. H. Bang, J. Solid State Chem., 2022, 315, 123510.
- 54 H. Siddiqui, Ion Beam Techniques and Applications, Intech, 2019, DOI: 10.5772/intechopen.83566.
- 55 A. Zatirostami, Opt. Mater., 2021, 117, 111110.
- 56 T. M. Mukametkali, B. R. Ilyassov, A. K. Aimukhanov, T. M. Serikov, A. S. Baltabekov, L. S. Aldasheva and A. K. Zeinidenov, Phys. B Condens. Matter, 2023, 659, 414784.

57 W. Zhang, Y. Liu, D. Zhou, H. Wang, W. Liang and F. Yang, Beilstein J. Nanotechnol., 2016, 7, 1129–1140.

- 58 S. Jin, E. Shin and J. Hong, *Nanomaterials*, 2017, 7(10), 315.
- 59 H. G. Yang, G. Liu, S. Z. Qiao, C. H. Sun, Y. G. Jin, S. C. Smith, J. Zou, H. M. Cheng and G. Q. Lu, *J. Am. Chem. Soc.*, 2009, 131, 4078-4083.
- 60 P. V. Shinde, S. Gagare, C. S. Rout and D. J. Late, *RSC Adv.*, 2020, **10**, 29378–29384.
- 61 J. Liu, Q. Zhang, L. Niu, B. Hu and X. Zhou, *J. Mater. Sci. Mater. Electron.*, 2016, 27, 9115–9123.
- 62 D. C. Hurum, A. G. Agrios, K. A. Gray, T. Rajh and M. C. Thurnauer, J. Phys. Chem. B, 2003, 107, 4545-4549.
- 63 M. Landmann, E. Rauls and W. G. Schmidt, J. Phys. Condens. Matter, 2012, 24, 195503.
- 64 A. Zavabeti, A. Jannat, L. Zhong, A. A. Haidry, Z. Yao and J. Z. Ou, Two-Dimensional Materials in Large-Areas: Synthesis, Properties and Applications, Springer Singapore, 2020, vol. 12.
- 65 V. Shanmugam, R. A. Mensah, K. Babu, S. Gawusu, A. Chanda, Y. Tu, R. E. Neisiany, M. Försth, G. Sas and O. Das, *Part. Part. Syst. Charact.*, 2022, 39(6), 2200031.
- 66 A. F. Da Silva, N. S. Dantas, E. F. Da Silva, I. Pepe, M. O. Torres, C. Persson, T. Lindgren, J. S. De Almeida and R. Ahuja, AIP Conf. Proc., 2005, 772, 177–178.
- 67 W. Guo, Y. Shen, G. Boschloo, A. Hagfeldt and T. Ma, *Electrochim. Acta*, 2011, **56**, 4611–4617.
- 68 S. Iijima, Nature, 1991, 354, 56-58.
- 69 M. Law, L. E. Greene, J. C. Johnson, R. Saykally and P. Yang, Nat. Mater., 2005, 4, 455–459.
- 70 D. Joshy, S. B. Narendranath, Y. A. Ismail and P. Periyat, *Nanoscale Adv.*, 2022, 73, 5202–5232.
- 71 X. Feng, K. Shankar, O. K. Varghese, M. Paulose, T. J. Latempa and C. A. Grimes, *Nano Lett.*, 2008, **8**, 3781–3786.
- 72 W. Liu, H. Lu, M. Zhang and M. Guo, *Appl. Surf. Sci.*, 2015, 347, 214–223.
- 73 A. M. Bakhshayesh, M. R. Mohammadi, H. Dadar and D. J. Fray, *Electrochim. Acta*, 2013, **90**, 302–308.
- 74 C. Zha, L. Shen, X. Zhang, Y. Wang, B. A. Korgel, A. Gupta and N. Bao, ACS Appl. Mater. Interfaces, 2014, 6, 122–129.
- 75 W. Q. Wu, Y. F. Xu, C. Y. Su and D. Bin Kuang, *Energy Environ. Sci.*, 2014, 7, 644–649.
- 76 Y. C. Yen, P. H. Chen, J. Z. Chen, J. A. Chen and K. J. Lin, ACS Appl. Mater. Interfaces, 2015, 7, 1892–1898.
- 77 W. Q. Wu, Y. F. Xu, H. S. Rao, C. Y. Su and D. Bin Kuang, J. Am. Chem. Soc., 2014, 136, 6437–6445.
- 78 D. K. Roh, W. S. Chi, S. H. Ahn, H. Jeon and J. H. Kim, *ChemSusChem*, 2013, **6**, 1384–1391.
- 79 H. Li, Q. Yu, Y. Huang, C. Yu, R. Li, J. Wang, F. Guo, S. Jiao, S. Gao, Y. Zhang, X. Zhang, P. Wang and L. Zhao, ACS Appl. Mater. Interfaces, 2016, 8, 13384–13391.
- 80 S. Ni, D. Wang, F. Guo, S. Jiao, Y. Zhang, J. Wang, B. Wang, L. Yuan, L. Zhang and L. Zhao, *J. Cryst. Growth*, 2019, 505, 62–68.
- 81 J. Jiu, S. Isoda, F. Wang and M. Adachi, *J. Phys. Chem. B*, 2006, **110**, 2087–2092.

- 82 L. De Marco, M. Manca, R. Giannuzzi, F. Malara, G. Melcarne, G. Ciccarella, I. Zama, R. Cingolani and G. Gigli, J. Phys. Chem. C, 2010, 114, 4228-4236.
- 83 W. Zhang, Y. Xie, D. Xiong, X. Zeng, Z. Li, M. Wang, Y. B. Cheng, W. Chen, K. Yan and S. Yang, ACS Appl. Mater. Interfaces, 2014, 6, 9698–9704.
- 84 J. Liu, J. Luo, W. Yang, Y. Wang, L. Zhu, Y. Xu, Y. Tang, Y. Hu, C. Wang, Y. Chen and W. Shi, J. Mater. Sci. Technol., 2015, 31, 106–109.
- 85 B. H. Lee, M. Y. Song, S. Y. Jang, S. M. Jo, S. Y. Kwak and D. Y. Kim, *J. Phys. Chem. C*, 2009, **113**, 21453–21457.
- 86 L. Yang and W. W. F. Leung, *Adv. Mater.*, 2013, **25**, 1792–1795.
- 87 X. Chen, Q. Du, W. Yang, W. Liu, Z. Miao and P. Yang, *J. Solid State Electrochem.*, 2018, **22**, 685–691.
- 88 M. R. Subramaniam, D. Kumaresan, S. Jothi, J. D. McGettrick and T. M. Watson, *Appl. Surf. Sci.*, 2018, 428, 439–447.
- 89 Y. Tang, C. Wang, Y. Hu, L. Huang, J. Fu and W. Yang, Superlattices Microstruct., 2016, 89, 1–6.
- 90 J. Jiu, F. Wang, S. Isoda and M. Adachi, *Chem. Lett.*, 2005, 34, 1506–1507.
- 91 S. Chatterjee, W. A. Webre, S. Patra, B. Rout, G. A. Glass, F. D'Souza and S. Chatterjee, *J. Alloys Compd.*, 2020, **826**, 154188.
- 92 H. Y. Chen, T. L. Zhang, J. Fan, D. Bin Kuang and C. Y. Su, *ACS Appl. Mater. Interfaces*, 2013, 5, 9205–9211.
- 93 Y. Rui, Y. Li, Q. Zhang and H. Wang, *Nanoscale*, 2013, 5, 12574–12581.
- 94 S. Kathirvel, C. Su, Y. J. Shiao, Y. F. Lin, B. R. Chen and W. R. Li, *Sol. Energy*, 2016, **132**, 310–320.
- 95 N. Sriharan, T. S. Senthil, M. Kang and N. M. Ganesan, *Appl. Phys. A Mater. Sci. Process.*, 2019, **125**, 1–10.
- 96 N. Liu, X. Chen, J. Zhang and J. W. Schwank, *Catal. Today*, 2014, 225, 34–51.
- 97 H. Cheng, Y. Feng, Y. Fu, Y. Zheng, Y. Shao and Y. Bai, *J. Mater. Chem. C*, 2022, **10**, 13590–13610.
- 98 J. Wang and Z. Lin, Chem. Mater., 2010, 22, 579-584.
- 99 B. X. Lei, J. Y. Liao, R. Zhang, J. Wang, C. Y. Su and D. Bin Kuang, *J. Phys. Chem. C*, 2010, **114**, 15228–15233.
- 100 H. Park, W. R. Kim, H. T. Jeong, J. J. Lee, H. G. Kim and W. Y. Choi, Sol. Energy Mater. Sol. Cells, 2011, 95, 184–189.
- 101 P. Roy, D. Kim, I. Paramasivam and P. Schmuki, *Electrochem. commun.*, 2009, **11**, 1001–1004.
- 102 Z. He, W. Que, P. Sun and J. Ren, *ACS Appl. Mater. Interfaces*, 2013, 5, 12779–12783.
- 103 N. Fu, X. Jiang, D. Chen, Y. Duan, G. Zhang, M. Chang, Y. Fang and Y. Lin, *J. Power Sources*, 2019, **439**, 227076.
- 104 B. Bozkurt Çırak, Ç. Eden, Y. Erdoğan, Z. Demir, K. V. Özdokur, B. Caglar, S. Morkoç Karadeniz, T. Kılınç, A. Ercan Ekinci and Ç. Çırak, Optik, 2020, 203, 163963.
- 105 W. Q. Wu, Y. F. Xu, H. S. Rao, C. Y. Su and D. Bin Kuang, *J. Phys. Chem. C*, 2014, **118**, 16426–16432.
- 106 M. Abdullah and S. K. Kamarudin, *Renew. Sustain. Energy Rev.*, 2017, **76**, 212–225.
- 107 M. Adachi, Y. Murata, I. Okada and S. Yoshikawa, J. Electrochem. Soc., 2003, 150, G488.

108 Q. Zheng, H. Kang, J. Yun, J. Lee, J. H. Park and S. Baik, ACS 131

Nano, 2011, 5, 5088–5093.

RSC Advances

- 109 J. H. Hu, S. Q. Tong, Y. P. Yang, J. J. Cheng, L. Zhao and J. X. Duan, *Acta Metall. Sin.*, 2016, 29, 840–847.
- 110 J. Khan, J. Gu, S. He, X. Li, G. Ahmed, Z. Liu, M. N. Akhtar, W. Mai and M. Wu, *Nanoscale*, 2017, 9, 9913–9920.
- 111 W. Zhu, Y. Liu, A. Yi, M. Zhu, W. Li and N. Fu, *Electrochim. Acta*, 2019, **299**, 339–345.
- 112 R. Asahi, Y. Taga and W. Mannstadt, *Phys. Rev. B Condens. Matter Mater. Phys.*, 2000, **61**, 7459–7465.
- 113 T. Umebayashi, T. Yamaki, H. Itoh and K. Asai, *J. Phys. Chem. Solids*, 2002, **63**, 1909–1920.
- 114 A. Khlyustova, N. Sirotkin, T. Kusova, A. Kraev, V. Titov and A. Agafonov, *Mater. Adv.*, 2020, 1, 1193–1201.
- 115 H.-W. Ju, J.-W. Kwon, D.-N. Lee, Y.-J. Park, S.-E. Lee and T. Kim, *Adv. Power Technol.*, 2024, 35, 104406.
- 116 M. Ayaz, A. S. Alatawi, M. Hijji, M. A. Namazi and M. I. M. Ershath, *J. Phys. Chem. Solids*, 2024, **188**, 111913.
- 117 A. M. Sharif, M. Ashrafuzzaman, A. Kalam, A. G. Al-Sehemi, P. Yadav, B. Tripathi, M. Dubey and G. Du, *Materials*, 2023, 16(17), 5731.
- 118 R. M. Novianti, N. M. Nursam, S. Shobih, J. Hidayat and S. Soepriyanto, *Metalurgi*, 2023, 38, 1–8.
- 119 T. Rajaramanan, F. Heidari Gourji, D. Velauthapillai, P. Ravirajan and M. Senthilnanthanan, *Int. J. Energy Res.*, 2023, 1–12, DOI: 10.1155/2023/1090174.
- 120 K. K. Tehare, S. T. Navale, F. J. Stadler, Z. He, H. Yang, X. Xiong, X. Liu and R. S. Mane, *Mater. Res. Bull.*, 2018, 99, 491–495.
- 121 T. R. Naveen Kumar, S. Yuvaraj, P. Kavitha, V. Sudhakar, K. Krishnamoorthy and B. Neppolian, *Sol. Energy*, 2020, **201**, 965–971.
- 122 A. Babu, A. Vasanth, S. Nair and M. Shanmugam, *J. Semicond.*, 2021, **42**, 052701.
- 123 A. K. Kaliamurthy, F. K. Asiam, B. Yadagiri, C. Chen, H. C. Kang, S. Sandhu, M. Z. Qamar, K. Yoo and J. J. Lee, *ACS Appl. Energy Mater.*, 2024, 7, 1983–1992.
- 124 D. F. S. L. Rodrigues, J. Martins, F. Sauvage, C. M. R. Abreu, J. F. J. Coelho, A. C. Serra, D. Ivanou and A. Mendes, Surfaces and Interfaces, 2024, 103627, DOI: 10.1016/ j.surfin.2023.103627.
- 125 I. Singh, V. Bhullar and A. Mahajan, *Energy and Fuels*, 2023, 37, 15054–15066.
- 126 H. G. Lemos, R. M. Ronchi, G. R. Portugal, J. H. H. Rossato, G. S. Selopal, D. Barba, E. C. Venancio, F. Rosei, J. T. Arantes and S. F. Santos, ACS Appl. Energy Mater., 2022, 5, 15928–15938.
- 127 S. P. Nagalingam, S. Pandiaraj, A. N. Alodhayb and A. N. Grace, *Nanoscale*, 2024, **16**, 13121–13130.
- 128 H. Yan, M. Chen, W. Liu, P. Wang, M. Liu, Y. Liu, L. Ye and M. Gu, *Opt. Mater.*, 2023, **140**, 113902.
- 129 S. Priya Nagalingam and A. N. Grace, *Mater. Today Chem.*, 2022, **26**, 101113.
- 130 S. P. Nagalingam, S. Pandiaraj, K. E. Alzahrani, A. N. Alodhayb and A. N. Grace, *RSC Adv.*, 2024, 14, 24000-24009.

- 131 H. Wang, M. Liu, M. Zhang, P. Wang, H. Miura, Y. Cheng and J. Bell, *Phys. Chem. Chem. Phys.*, 2011, 13, 17359–17366.
- 132 M. Yang, D. Kim, H. Jha, K. Lee, J. Paul and P. Schmuki, *Chem. Commun.*, 2011, 47, 2032–2034.
- 133 S. So, K. Lee and P. Schmuki, *Phys. Status Solidi Rapid Res. Lett.*, 2012, **6**, 169–171.
- 134 L. De Marco, M. Manca, R. Giannuzzi, M. R. Belviso, P. D. Cozzoli and G. Gigli, *Energy Environ. Sci.*, 2013, 6, 1791–1795.
- 135 K. Lee, A. Mazare and P. Schmuki, *Chem. Rev.*, 2014, **114**, 9385–9454.
- 136 Y. Tachibana, J. E. Moser, M. Grätzel, D. R. Klug and J. R. Durrant, *J. Phys. Chem.*, 1996, **100**, 20056–20062.
- 137 N. J. Cherepy, G. P. Smestad, M. Grätzel and J. Z. Zhang, *J. Phys. Chem. B*, 1997, **101**, 9342–9351.
- 138 M. Hilgendorff and V. Sundström, *J. Phys. Chem. B*, 1998, **102**, 10505–10514.
- 139 A. Hagfeldt and M. Grätzel, *Acc. Chem. Res.*, 2000, **33**, 269–277.
- 140 B. O'Regan, J. Moser, M. Anderson and M. Grätzel, *J. Phys. Chem.*, 1990, **94**, 8720–8726.
- 141 D. Cahen, G. Hodes, M. Grätzel, J. F. Guillemoles and I. Riess, *J. Phys. Chem. B*, 2000, **104**, 2053–2059.
- 142 A. Zaban, S. Ferrere and B. A. Gregg, *J. Phys. Chem. B*, 1998, **102**, 452–460.
- 143 A. Zaban, A. Meier and B. A. Gregg, *J. Phys. Chem. B*, 1997, **101**, 7985–7990.
- 144 K. Schwarzburg and F. Willig, *J. Phys. Chem. B*, 1999, **103**, 5745–5746.
- 145 J. Bisquert, G. Garcia-Belmonte and F. Fabregat-Santiago, *J. Solid State Electrochem.*, 1999, 3, 337–347.
- 146 J. Ferber and J. Luther, *J. Phys. Chem. B*, 2002, **105**, 4895–4903.
- 147 H. Gerischer, *Physical Chemistry: An Advanced Treatise*, Academic Press-New York-London, 1970, pp. 487–489.
- 148 M. L. Rosenbluth and N. S. Lewis, *J. Phys. Chem.*, 1989, **93**, 3735–3740.
- 149 J. Pleskov, Y. Gurevich and P. Bartlett, *Semiconductor Photoelectrochemistry*, New York Consulting Bureau, 1986, pp. 135–138.
- 150 W. Shockley, Bell Syst. Tech. J., 1949, 28, 435.
- 151 A. Hagfeldtt and M. Gratzel, Chem. Rev., 1995, 95, 49-68.
- 152 G. Kron, T. Egerter, J. H. Werner and U. Rau, *J. Phys. Chem. B*, 2003, **107**, 3556–3564.
- 153 A. Soussi, A. Ait Hssi, M. Boujnah, L. Boulkadat, K. Abouabassi, A. Asbayou, A. Elfanaoui, R. Markazi, A. Ihlal and K. Bouabid, *J. Electron. Mater.*, 2021, **50**, 4497–4510.
- 154 Y. M. Evtushenko, S. V. Romashkin, N. S. Trofimov and T. K. Chekhlova, *Phys. Procedia*, 2015, 73, 100–107.
- 155 M. I. Khan, K. A. Bhatti, R. Qindeel, H. S. Althobaiti and N. Alonizan, *Results Phys.*, 2017, 7, 1437–1439.
- 156 R. Qian, H. Zong, J. Schneider, G. Zhou, T. Zhao, Y. Li, J. Yang, D. W. Bahnemann and J. H. Pan, *Catal. Today*, 2019, 335, 78–90.
- 157 F. Yang, J. Xi, L. Y. Gan, Y. Wang, S. Lu, W. Ma, F. Cai, Y. Zhang, C. Cheng and Y. Zhao, *J. Colloid Interface Sci.*, 2016, 464, 1–9.

158 A. Al Mayyahi, B. M. Everhart, T. B. Shrestha, T. C. Back and P. B. Amama, *RSC Adv.*, 2021, **11**, 11702–11713.

- 159 P. Wadhwa, S. Kumar, T. J. D. Kumar, A. Shukla and R. Kumar, *Condens. Matter*, 2018, 3, 1–10.
- 160 S. Singh Surah, M. Vishwakarma, R. Kumar, R. Nain, S. Sirohi and G. Kumar, *Results Phys.*, 2019, 12, 1725–1731.
- 161 B. Minhas, S. Dino, H. Qian and Y. Zuo, *Surf. Coatings Technol.*, 2020, **395**, 125932.
- 162 D. J. Mowbray, J. I. Martinez, G. J. M. Lastra, K. S. Thygesen and K. W. Jacobsen, *J. Phys. Chem. C*, 2009, **113**, 12301–12308.
- 163 P. K. Das, A. K. Mallik, A. H. Molla, A. K. Santra, R. Ganguly, A. Saha, S. Kumar and V. K. Aswal, *J. Therm. Anal. Calorim.*, 2022, 147, 5617–5635.

- 164 S. C. Poh, H. Ahmad, C. H. Ting, H. T. Tung and H. K. Jun, *J. Mater. Sci. Mater. Electron.*, 2021, **32**, 12031–12041.
- 165 J. Gong, K. Sumathy, Q. Qiao and Z. Zhou, *Renew. Sustain. Energy Rev.*, 2017, **68**, 234–246.
- 166 S. Mozaffari, M. R. Nateghi and M. B. Zarandi, *Renew. Sustain. Energy Rev.*, 2017, 71, 675–686.
- 167 T. Chen, J. Xie and P. Gao, *Adv. Energy Sustain. Res.*, 2022, 2100218, DOI: 10.1002/aesr.202100218.
- 168 I. Groeneveld, M. Kanelli, F. Ariese and M. R. van Bommel, *Dye. Pigment.*, 2023, **210**, 110999.
- 169 K. M. Reza, A. Kurny and F. Gulshan, Appl. Water Sci., 2017, 7, 1569–1578.
- 170 P. D. Sekaran and R. Marimuthu, *Brazilian J. Phys.*, 2024, 54, 1–10.