


Cite this: *RSC Adv.*, 2025, 15, 10390

# Ni–Co bimetallic phosphide catalyst toward electrocatalytic ammonia synthesis under ambient conditions†

Dongnan Zhao,<sup>‡ab</sup> Zhixian Mao,<sup>‡bc</sup> Shengbo Zhang,<sup>id\*bc</sup> Min Liu,<sup>b</sup> Kui Hu,<sup>b</sup> Daopeng Li,<sup>bc</sup> Zhengguo Qu,<sup>b</sup> Li Zhou<sup>bc</sup> and Tongfei Shi<sup>\*bc</sup>

Electrocatalytic nitrate reduction reaction (NitRR) under ambient conditions is a promising sustainable and eco-friendly method for ammonia (NH<sub>3</sub>) synthesis, which currently highly relies on the energy-consuming Haber–Bosch process with enormous CO<sub>2</sub> emissions. In this work, we report the synthesis of a Ni–Co bimetallic phosphide catalyst (NiCoP) using the traditional hydrothermal combined high-temperature phosphorization method. Compared with monometallic phosphides such as Ni<sub>2</sub>P and CoP, the as-synthesized NiCoP catalyst with synergistic effects exhibits remarkable NitRR performance with the highest faradaic efficiency (FE) of 91.3 ± 4.4% at –1.2 V (vs. RHE) with the maximum NH<sub>3</sub> yield rate of 5553.4 ± 400.8 μg h<sup>–1</sup> cm<sup>–2</sup> at –1.4 V (vs. RHE). Further *in situ* different electrochemical mass spectrometry (DEMS) analysis is employed to identify the intermediate produced during the electrocatalytic NitRR process, confirming NiCoP as a promising electrocatalyst for NH<sub>3</sub> synthesis.

Received 16th January 2025

Accepted 29th March 2025

DOI: 10.1039/d5ra00391a

rsc.li/rsc-advances

Ammonia (NH<sub>3</sub>) has a wide range of applications in various industries, including dyes, synthetic fibers, and nitric acid production.<sup>1</sup> The Haber–Bosch process is the conventional approach employed in the industrial synthesis of NH<sub>3</sub>.<sup>2,3</sup> This approach consumes substantial amounts of energy while generating significant quantities of CO<sub>2</sub>, which hinders the achievement of “dual carbon” goals encompassing peak carbon emissions followed by carbon neutrality.<sup>4</sup> Therefore, there is an urgent need to discover a new efficient clean synthesis method for NH<sub>3</sub> synthesis at this stage.<sup>5</sup> Currently, there are several emerging research directions in the field of NH<sub>3</sub> synthesis.<sup>6,7</sup> The primary areas of focus include electrochemical nitrogen/nitrate reduction reaction (NitRR/NRR).<sup>8</sup> Among these, NRR benefits from abundant nitrogen sources. However, the formidable challenge lies in breaking the strong triple bond of N≡N due to its high dissociation energy, compounded by N<sub>2</sub>'s limited solubility in water.<sup>9</sup> These constraints significantly impede both production yield and faradaic efficiency (FE) of NH<sub>3</sub> synthesis. On the other hand, NitRR overcomes the limitation posed by

low solubility of N<sub>2</sub> in aqueous environments. Furthermore, compared to the dissociation energy (941 kJ mol<sup>–1</sup>) required for breaking the triple bond in N≡N, nitrate reduction benefits from a lower dissociation energy (204 kJ mol<sup>–1</sup>) for breaking the double bond in N=O during catalytic reactions facilitated by electrochemical processes.<sup>10,11</sup>

Transition-metal phosphides (TMPs) have recently emerged as one type of earth-abundant electrocatalyst with impressive activity.<sup>12,13</sup> Considerable attention has been paid to these types of catalysts due to their excellent electronic conductivity, hybrid orbitals, and low cost.<sup>14</sup> Additionally, in the process of forming transition metal phosphides, with the relatively large radius of phosphorus atoms, stable interstitial compounds are challenging to form. Therefore, phosphorus atoms occupy internal structural units in metals through radius filling, exposing more coordination unsaturated surface atoms.<sup>15</sup> An increased number of active sites leads to enhanced catalytic activity. For instance, Ni<sub>2</sub>P with (111) crystal plane grown *in situ* on nickel foam (NFP) serves as a high-performance catalyst for NitRR,<sup>16</sup> exhibiting a NH<sub>3</sub> yield rate (*R*<sub>NH<sub>3</sub></sub>) of 0.056 mmol h<sup>–1</sup> mg<sup>–1</sup> and a FE reaching up to 99.23%.<sup>17</sup> Besides, Sun and co-workers reported a Co<sub>1</sub>-P/NPG catalyst and demonstrated the Co atoms serve as the main NO<sub>3</sub><sup>–</sup> activation sites,<sup>18</sup> while the P atoms can regulate the distribution of water at the catalyst's surface and simultaneously promote water dissociation, accelerating the proton-coupled electron transfer (PCET) kinetics of NitRR to achieve a *R*<sub>NH<sub>3</sub></sub> of 8.6 mg h<sup>–1</sup> mg<sup>–1</sup> with a FE of 93.8%.<sup>19</sup> These findings hold significant implications for electrocatalysis research focused on studying TMPs.

<sup>a</sup>School of Energy Materials and Chemical Engineering, Hefei University, Hefei 230601, China

<sup>b</sup>Key Laboratory of Materials Physics, Centre for Environmental and Energy Nanomaterials, Anhui Key Laboratory of Nanomaterials and Nanotechnology, CAS Center for Excellence in Nanoscience Institute of Solid State Physics, HFIPS, Chinese Academy of Sciences, Hefei 230031, China. E-mail: tfshi@issp.ac.cn; shbzhang@issp.ac.cn

<sup>c</sup>University of Science and Technology of China, Hefei 230026, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d5ra00391a>

‡ These authors contributed equally to this work.



Inspired by the aforementioned work, we successfully synthesized a Ni–Co bimetallic phosphide catalyst (NiCoP) for the electrocatalytic reduction of nitrate to produce  $\text{NH}_3$ . Compared with monometallic phosphides such as  $\text{Ni}_2\text{P}$  and  $\text{CoP}$ , NiCoP exhibited enhanced performance in  $\text{NH}_3$  synthesis. As a result, the as-synthesized NiCoP affords an excellent  $R_{\text{NH}_3}$  of  $5553.4 \pm 400.8 \mu\text{g h}^{-1} \text{cm}^{-2}$  at  $-1.4 \text{ V}$  (vs. RHE) and a maximum FE of  $91.3 \pm 4.4$  at  $-1.2 \text{ V}$  (vs. RHE), with outstanding stability during 10 h NitRR. The  $^{15}\text{N}$  isotope labeling experiments confirmed that the produced  $\text{NH}_3$  indeed originated from the nitrate reduction reaction catalyzed by NiCoP.

Fig. 1a illustrates the synthetic process of the NiCoP catalyst using the traditional hydrothermal combined high-temperature phosphorization method. For meaningful comparison,  $\text{Ni}_2\text{P}$  and  $\text{CoP}$  were also fabricated using similar synthetic method (Fig. S1, ESI†). The X-ray diffraction (XRD) pattern of the synthesized NiCoP sample is presented in Fig. 1b. The observed peaks at  $2\theta = 40.9^\circ$ ,  $44.9^\circ$ ,  $47.6^\circ$  and  $54.4^\circ$  correspond to the crystal planes (111), (201), (210) and (300) of NiCoP (JCPDS Card No. 04-001-6153),<sup>20</sup> respectively. The high-resolution transmission electron microscopy (HR-TEM) image shown in Fig. 1c reveals a lattice spacing approximately equal to 0.21 nm corresponding to the crystal plane (111) of NiCoP as consistent with XRD results. The high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) along with elemental mapping images (Fig. 1d and e), further corroborate the homogeneous distribution of P, O, Ni and Co elements over the entire sample, further confirming the formation of NiCoP.

The as-synthesized NiCoP sample exhibits favorable mesoporous and microporous structures (Fig. S2, ESI†), which is beneficial for exposing of more active sites and facilitates charge transfer during electrocatalytic processes.<sup>21</sup> Surface composition and oxidation states of NiCoP were investigated using X-ray photoelectron spectroscopy (XPS) (Table S1, ESI†). Fig. 2a displays the XPS spectrum obtained from the surface measurement, indicating the presence of Ni, Co, O, and P elements. Fig. 2b shows the high-resolution XPS spectra of Ni

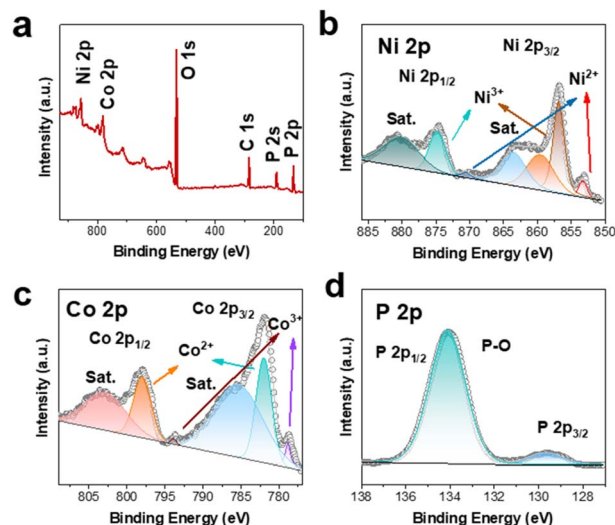


Fig. 2 (a) Surface survey XPS spectrum of NiCoP. High-resolution (b) Ni 2p, (c) Co 2p, and (d) P 2p spectra of NiCoP.

2p, where Ni  $2p_{3/2}$  peaks at 853.3 eV and 856.8 eV correspond to  $\text{Ni}^{2+}$  and  $\text{Ni}^{3+}$ , respectively;<sup>22</sup> while peaks at 870.6 eV and 874.7 eV belong to  $\text{Ni}^{2+}$  and  $\text{Ni}^{3+}$  in the case of Ni  $2p_{1/2}$ ;<sup>23</sup> the satellite peaks are observed at binding energies around 880.1 eV and 863.5 eV in combination with 859.5 eV.<sup>24</sup> The high-resolution XPS spectra of Co 2p is depicted in Fig. 2c, wherein the Co  $2p_{3/2}$  peak encompasses both  $\text{Co}^{3+}$  (778.8 eV) and  $\text{Co}^{2+}$  (782.0 eV), while the peaks at 793.8 eV for  $\text{Co}^{3+}$  and 797.9 eV for  $\text{Co}^{2+}$  correspond to the Co  $2p_{1/2}$  state. The peaks observed at 785.3 eV and 802.8 eV are identified as satellite peaks. In Fig. 2d, a P–O peak is discernible at a binding energy of 134.1 eV, which likely originates from phosphate compounds,<sup>25</sup> whereas the peak at 129.6 eV corresponds to P  $2p_{3/2}$ .<sup>26</sup> The above XPS results further confirm the formation of NiCoP after phosphorization treatment. Furthermore, we characterized  $\text{Ni}_2\text{P}$  and  $\text{CoP}$  using XPS spectroscopy (Fig. S3, ESI†). In comparison with  $\text{CoP}$ , NiCoP exhibits  $\text{Co}^{3+}$  species, which offer additional empty d orbitals. This characteristic enhances the affinity for  $\text{H}_{\text{ads}}$ , thereby promoting NitRR.

The electrochemical NitRR performance of the as-synthesized NiCoP was investigated under ambient temperature and pressure in a standard three-electrode H-type cell. The linear sweep voltammetry (LSV) curves in Ar-saturated 0.1 M  $\text{Na}_2\text{SO}_4$  electrolyte with or without  $\text{NO}_3^-$  were first measured to examine the catalytic responsiveness of  $\text{NO}_3^-$ . As depicted in Fig. 3a, when  $\text{NO}_3^-$  was present in the electrolyte solution, the increase of current density is due to the excellent correspondence of the NiCoP catalyst to  $\text{NO}_3^-$  at the reduction potential. Constant potential electrolysis ranging from  $-0.8 \text{ V}$  to  $-1.4 \text{ V}$  (vs. RHE) were selected to further quantitatively assess  $\text{NH}_3$  electrosynthesis activity. The time dependent current density curves recorded for 2 h at various potentials illustrate the superior stability of NiCoP (Fig. S4, ESI†). In this study, the main product  $\text{NH}_3$  and by-product  $\text{NO}_2^-$  and  $\text{NH}_3$  were quantified by UV-vis spectrophotometry with calibration curves (Fig. S5 and S6, ESI†). As shown in Fig. 3b, the catalytic NiCoP

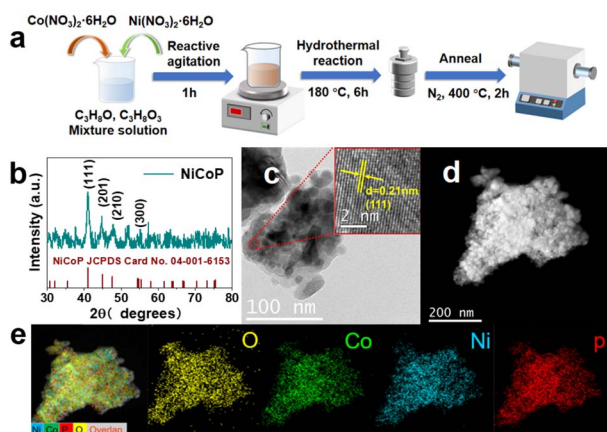


Fig. 1 (a) Schematic diagram illustrating the synthetic procedure of NiCoP. (b) XRD pattern and (c) TEM image (inset is the HR-TEM image) of NiCoP. (d) HAADF-STEM image and (e) corresponding elemental mapping images of NiCoP.

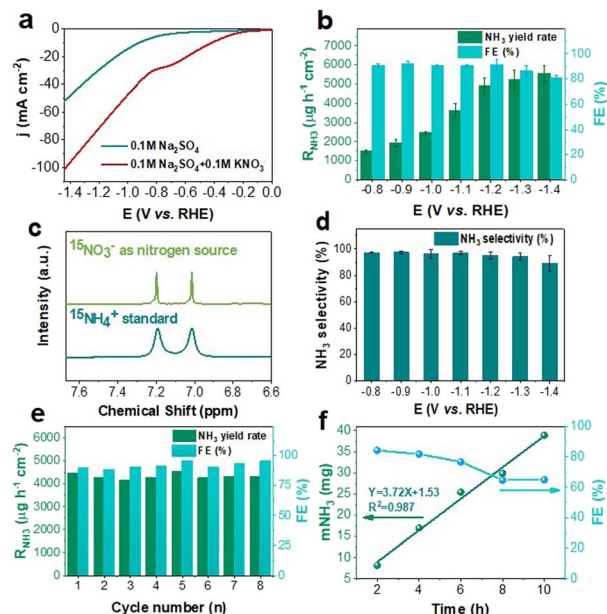


Fig. 3 (a) LSV curves of NiCoP catalyst in 0.1 M  $\text{Na}_2\text{SO}_4$  and 0.1 M  $\text{Na}_2\text{SO}_4 + 0.1 \text{ M KNO}_3$  solution. (b)  $R_{\text{NH}_3}$  and FE of NiCoP catalyst obtained at different potentials for 2 h NitRR measurement. (c)  $^{15}\text{H}$  NMR spectra of NiCoP catalyst using  $^{15}\text{NO}_3^-$  as nitrogen source for NitRR and standards ( $^{15}\text{NH}_4^+$ ) $_2\text{SO}_4$ . (d)  $S_{\text{NH}_3}$  of NiCoP catalyst obtained at different potentials. (e) Recycling tests for NiCoP catalyst during NitRR at  $-1.2 \text{ V}$  (vs. RHE). (f) The FE and  $\text{NH}_3$  yield were monitored over a 10 h NitRR conducted at  $-1.2 \text{ V}$  (vs. RHE).

catalyst result in remarkable  $\text{NH}_3$  yield rate ( $R_{\text{NH}_3}$ ) of  $5553.4 \pm 400.8 \mu\text{g h}^{-1} \text{cm}^{-2}$  at  $-1.4 \text{ V}$  (vs. RHE), and the superior faradaic efficiency (FE) of  $91.3 \pm 4.4\%$  at  $-1.2 \text{ V}$  (vs. RHE), superior to the most reported NitRR electrocatalysts (Table S2 and Fig. S7, ESI†). Both the  $R_{\text{NH}_3}$  and the FE were times higher than those of  $\text{Ni}_2\text{P}$  ( $R_{\text{NH}_3}$ :  $1807.2 \mu\text{g h}^{-1} \text{cm}^{-2}$ ; FE: 54.6%) and CoP ( $R_{\text{NH}_3}$ :  $3600.1 \mu\text{g h}^{-1} \text{cm}^{-2}$ ; FE: 90.3%) (Fig. S8, ESI†), which is attributed to synergistic effect of Ni-Co bimetallic catalyst.<sup>27</sup>

In addition, LSV tests were also conducted on  $\text{Ni}_2\text{P}$  and CoP (Fig. S9, ESI†). At the same potential, the current densities of  $\text{Ni}_2\text{P}$  and CoP were both lower than that of NiCoP. These experimental results further substantiate the aforementioned conclusion. To verify the source of ammonium,  $^{15}\text{N}$  isotope labeling experiments are conducted.<sup>28</sup> As shown in Fig. 3c, the  $^1\text{H}$  nuclear magnetic resonance (NMR) spectra of electrolyte adopting  $^{15}\text{NO}_3^-$  as reactants show typical double peaks of  $^{15}\text{NH}_4^+$ . In addition, we also conducted other representative control experiments, including: (1) open circuit potential (OCP), (2) 0.1 M  $\text{Na}_2\text{SO}_4$  electrolyte without  $\text{NO}_3^-$  and (3) blank carbon paper (CP) without NiCoP catalyst (Fig. S10, ESI†). The control experiments can effectively diagnose possible errors caused by environmental influences including raw material, electrolyte, catalyst decomposition, and other factors. Obviously, the extremely low absorbance obtained by the indophenol blue method confirms the validity of our experimental process and results (Fig. S11, ESI†).

Moreover, due to the low levels of  $\text{NO}_2^-$  detected ( $<0.056 \text{ mM}$ ) after NitRR at all applied potentials (Fig. S5, ESI†), the

selectivity of  $\text{NH}_3$  ( $S_{\text{NH}_3}$ ) of NiCoP at different applied potentials was calculated as displayed in Fig. 3d. The  $S_{\text{NH}_3}$  of NiCoP can reach the maximum FE of  $97.4 \pm 0.8\%$  at  $-0.9 \text{ V}$  (vs. RHE) and excellent FE of  $\text{NH}_3$  over 95% under a broad range from  $-0.8$  to  $-1.2 \text{ V}$  (vs. RHE) (Fig. 3d), indicating the high NitRR-to- $\text{NH}_3$  selectivity of NiCoP. Notably, when the applied potential exceeds  $-1.2 \text{ V}$  (vs. RHE), the  $R_{\text{NO}_2^-}$  increases, while both the FE and  $S_{\text{NH}_3}$  of NiCoP decrease significantly, primarily due to the occurrence of competitive hydrogen evolution reaction (HER) on NiCoP.<sup>29,30</sup> Besides superior activity, the durability of the catalyst is another crucial parameter for practical applications. As shown in Fig. 3e, both  $\text{NH}_3$  yields and FEs have no obvious fluctuation during 8 recycling tests at  $-1.2 \text{ V}$  (vs. RHE), confirming the high stability of NiCoP toward electrochemical NitRR. The corresponding UV-vis absorption spectra and current density curves are displayed in Fig. S12 (ESI†). Additionally, the superior durability of NiCoP for 10 h at  $-1.2 \text{ V}$  (vs. RHE) was confirmed by chronoamperometry measurements (Fig. S13, ESI†). The corresponding  $\text{NH}_3$  yield and time show a good linear relationship, with a slight decrease in FE (Fig. 3f). The LSV test was conducted on the reacted NiCoP (Fig. S14, ESI†), and its LSV curve basically coincides with that of the pre-reaction sample, further demonstrating the excellent stability of NiCoP. To determine the morphological and structural stability, careful examination of XRD, XPS and SEM characterizations on NiCoP after NitRR test (Fig. S15–S17, ESI†) confirms the high structural stability of NiCoP.

To further investigate the influence mechanism of the chemical microenvironment on catalytic activity, electrochemical impedance spectroscopy (EIS) and double-layer capacitance (DLC) tests were also performed (Fig. S18 and S19, ESI†). EIS measurements at various potentials revealed that NiCoP exhibits a lower charge transfer impedance at higher potentials, facilitating the efficient conversion of nitrate to ammonia under these conditions. The DLC test results for CoP,  $\text{Ni}_2\text{P}$ , and NiCoP reveal that the electrochemical surface area (ECSA) of NiCoP lies between those of  $\text{Ni}_2\text{P}$  and CoP. Despite having a lower ECSA compared to CoP, NiCoP exhibits superior NitRR performance. This demonstrates that the Ni-Co synergistic effect promotes the transformation of nitrate to ammonia. Furthermore, the *in situ* differential electrochemical mass spectrometry (DEMS) is employed for *in situ* detection of molecular intermediate and product over NiCoP.<sup>31</sup> The gaseous molecules can be identified based on  $m/z$  values, and the relative quantities of intermediates and products can be estimated in real-time based on signal intensity.<sup>32</sup> As shown in Fig. 4, the strongest  $m/z$  signals of 17 are recorded, which confirms the high  $\text{NH}_3$  selectivity of NiCoP. The signal intensity of the intermediate is significantly lower than that of  $\text{NH}_3$ , indicating that  $\text{NH}_3$  is the main product of NiCoP catalyst. The *in situ* DEMS results are inconsistent with the UV-vis results. This result suggests that the main reaction pathway of NitRR on NiCoP catalyst may be  $\text{NO}_3^- \rightarrow \text{*NO}_3 \rightarrow \text{*NO}_2 \rightarrow \text{*NO} \rightarrow \text{*N} \rightarrow \text{*NH} \rightarrow \text{*NH}_2 \rightarrow \text{*NH}_3 \rightarrow \text{NH}_3$  (g).

In conclusion, the Ni-Co bimetallic phosphide catalyst is experimentally proven as a superb NitRR electrocatalyst for ambient  $\text{NH}_3$  production with a large yield of  $5553.4 \pm 400.8 \mu\text{g}$





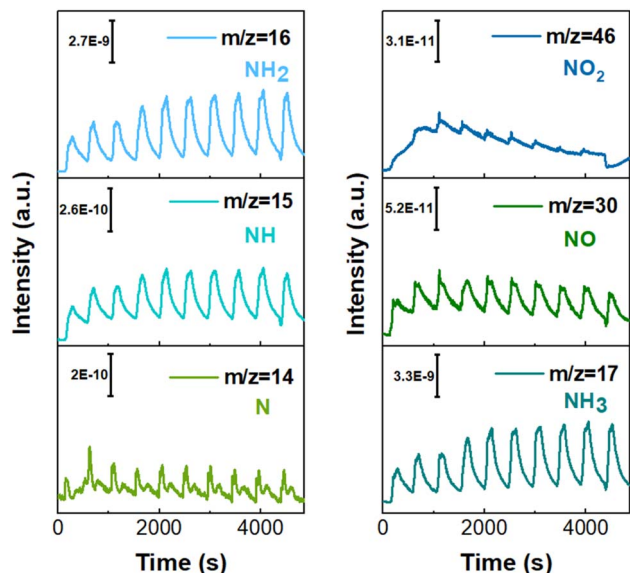


Fig. 4 *In situ* DEMS measurements of NitRR over NiCoP.

$\text{h}^{-1} \text{cm}^{-2}$  at  $-1.4 \text{ V}$  (vs. RHE) and a maximum FE of  $91.3 \pm 4.4$  at  $-1.2 \text{ V}$  (vs. RHE), respectively. The *in situ* DEMS analysis is employed to identify the intermediate produced during the electrocatalytic NitRR process, confirmed NiCoP as a promising electrocatalyst for  $\text{NH}_3$  synthesis. The results indicate that traditional hydrothermal combined high-temperature phosphorization can be considered as a promising method for the preparation of NitRR electrocatalysts. Meanwhile, this discovery promotes the application of transition-metal phosphides catalysts in room-temperature electrochemical reactions.

## Data availability

The data supporting this article have been included as part of the ESI.†

## Author contributions

Dongnan Zhao: conceptualization, investigation, visualization, writing – original draft. Shengbo Zhang: data curation, resources, supervision, writing – review & editing. Kui Hu: investigation, resources, formal analysis. Daopeng Li: investigation, resources, formal analysis. Zhixian Mao: investigation, resources, formal analysis. Min Liu: software. Zhengguo Qu: software. Li Zhou: software. Tongfei Shi: funding acquisition, supervision, resources, writing – review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was financially supported by the Natural Science Foundation of Anhui Provincial Natural Science Foundation (Grant No. 2408085MB021).

## Notes and references

- H. Zhang, H. Wang, X. Cao, M. Chen, Y. Liu, Y. Zhou, M. Huang, L. Xia, Y. Wang, T. Li, D. Zheng, Y. Luo, S. Sun, X. Zhao and X. Sun, *Adv. Mater.*, 2024, **36**, e2312746.
- J. Cao, Y. Hu, Y. Zheng, W. Zhang and B. Yu, *Front. Energy*, 2024, **18**, 128–140.
- H. Liu, L. Bai, A. Bergmann, B. R. Cuenya and J. Luo, *Chem*, 2024, **10**, 2963–2986.
- Y. Wang, C. Wang, M. Li, Y. Yu and B. Zhang, *Chem. Soc. Rev.*, 2021, **50**, 6720–6733.
- J. Martinez, A. Ortiz and I. Ortiz, *Appl. Catal., B*, 2017, **207**, 42–59.
- D. Liu, L. Qiao, S. Peng, H. Bai, C. Liu, W. F. Ip, K. H. Lo, H. Liu, K. W. Ng and S. Wang, *Adv. Funct. Mater.*, 2023, **33**, 2303480.
- J. Theerthagiri, J. Park, H. T. Das, N. Rahamathulla, E. S. F. Cardoso, A. P. Murthy, G. Maia, D. V. N. Vo and M. Y. Choi, *Environ. Chem. Lett.*, 2022, **20**, 2929–2949.
- O. Q. Carvalho, R. Marks, H. K. Nguyen, M. E. Vitale-Sullivan, S. C. Martinez, L. Árnadóttir and K. A. Stoerzinger, *J. Am. Chem. Soc.*, 2022, **144**, 14809–14818.
- Z. Wu, Y. Song, Y. Liu, W. Luo, W. Li and J. Yang, *Chem Catal.*, 2023, **3**, 100786.
- M. T. de Groot and M. T. M. Koper, *J. Electroanal. Chem.*, 2004, **562**, 81–94.
- Y. Zhao, Y. Liu, Z. Zhang, Z. Mo, C. Wang and S. Gao, *Nano Energy*, 2022, **97**, 107124.
- W. Wen, S. Fang, Y. Zhou, Y. Zhao, P. Li and X. Y. Yu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202408382.
- W. Zheng, L. Zhu, Z. Yan, Z. Lin, Z. Lei, Y. Zhang, H. Xu, Z. Dang, C. Wei and C. Feng, *Environ. Sci. Technol.*, 2021, **55**, 13231–13243.
- J. Zhou, S. Gao and G. Hu, *Energy Fuels*, 2024, **38**, 6701–6722.
- Q. Yao, J. Chen, S. Xiao, Y. Zhang and X. Zhou, *ACS Appl. Mater. Interfaces*, 2021, **13**, 30458–30467.
- R. Zhang, Y. Guo, S. Zhang, D. Chen, Y. Zhao, Z. Huang, L. Ma, P. Li, Q. Yang and G. Liang, *Adv. Energy Mater.*, 2022, **12**, 2103872.
- Q. Yao, J. Chen, S. Xiao, Y. Zhang and X. Zhou, *ACS Appl. Mater. Interfaces*, 2021, **13**, 30458–30467.
- J. Ni, J. Yan, F. Li, H. Qi, Q. Xu, C. Su, L. Sun, H. Sun, J. Ding and B. Liu, *Adv. Energy Mater.*, 2024, **14**, 2400065.
- J. Wu, J.-H. Li and Y.-X. Yu, *J. Phys. Chem. Lett.*, 2021, **12**, 3968–3975.
- Y. Lin, Y. Pan, S. Liu, K. Sun, Y. Cheng, M. Liu, Z. Wang, X. Li and J. Zhang, *Appl. Catal., B*, 2019, **259**, 118039.
- H. Xie, D. Jiang, H. Chen, X. Ma, X. Liu, Q. Qi and Y. Wang, *Nanoscale*, 2023, **15**, 7430–7437.
- Z. Zhou, L. Zeng, G. Xiong, L. Yang, H. Yuan, J. Yu, S. Xu, D. Wang, X. Zhang and H. Liu, *Chem. Eng. J.*, 2021, **426**, 129214.
- T. Liu, A. Li, C. Wang, W. Zhou, S. Liu and L. Guo, *Adv. Mater.*, 2018, **30**, 1803590.



- 24 S. Mahmood, M. S. Riaz, M. Ammar, Z. Wang, M. J. Iqbal, G. A. Ashraf, N. Afshan, N. Hassan, A. Bahadur and S. Iqbal, *Int. J. Hydrogen Energy*, 2024, **70**, 315–324.
- 25 J. Liang, W.-F. Hu, B. Song, T. Mou, L. Zhang, Y. Luo, Q. Liu, A. A. Alshehri, M. S. Hamdy, L.-M. Yang and X. Sun, *Inorg. Chem. Front.*, 2022, **9**, 1366–1372.
- 26 Y. Li, H. Zhang, M. Jiang, Y. Kuang, X. Sun and X. Duan, *Nano Res.*, 2016, **9**, 2251–2259.
- 27 J. Wang, J. Feng, T.-O. Soyol-Erdene, Z. Wei and W. Tang, *Sep. Purif. Technol.*, 2023, **320**, 124155.
- 28 Y. Zhao, R. Shi, X. Bian, C. Zhou, Y. Zhao, S. Zhang, F. Wu, G. I. N. Waterhouse, L.-Z. Wu, C.-H. Tung and T. Zhang, *Adv. Sci.*, 2019, **6**, 1802109.
- 29 Y. Zhang, X. Chen, W. Wang, L. Yin and J. C. Crittenden, *Appl. Catal., B*, 2022, **310**, 121346.
- 30 Y. Wang, W. Zhou, R. Jia, Y. Yu and B. Zhang, *Angew. Chem., Int. Ed.*, 2020, **59**, 5350–5354.
- 31 W.-J. Sun, L.-X. Li, H.-Y. Zhang, J.-H. He and J.-M. Lu, *ACS Sustain. Chem. Eng.*, 2022, **10**, 5958–5965.
- 32 Y. Wang, W. Yu, X. Li, J. Yu and W. Zhou, *Chem. Eng. J.*, 2023, **469**, 143889.

