


Cite this: *RSC Adv.*, 2025, 15, 28231

Traditional and photocatalytic conversion of aniline into azocompounds – a comprehensive experimental and theoretical review

Afsar Khan,^a Hong Ran,^a Chen Saisai,^a Nisar Muhammad,^a Adnan Abbas,^a Zhang Yi,^a Faheem Shah,^{*b} Weihua Chen^{*c} and Dayong Xu^{*a}

The catalytic conversion of aniline into azo compounds represents a significant and versatile route in synthetic organic chemistry, with applications spanning dyes, pharmaceuticals, and functional materials. This comprehensive review systematically examines recent advances in catalytic strategies for azo bond formation from aniline derivatives, encompassing homogeneous, heterogeneous, enzymatic, and photo-redox catalysis. Key mechanistic pathways, including oxidative coupling, dehydrogenative aromatization, and redox processes, are critically analyzed. The influence of catalyst design (e.g., transition metals, organo-catalysts, nanomaterials) and reaction conditions (solvent, oxidants, temperature) on selectivity and efficiency is discussed. Additionally, the review highlights sustainable approaches, such as aerobic oxidation and visible-light-driven catalysis, aligning with green chemistry principles. Challenges, including substrate scope limitations and scalability, are addressed, along with emerging trends and future prospects for industrial and academic applications. This work aims to serve as a foundational resource for researchers exploring catalytic azo compound synthesis.

Received 30th May 2025
Accepted 28th July 2025

DOI: 10.1039/d5ra03828f

rsc.li/rsc-advances

1 Introduction

Aromatic azo compounds are a significant class of molecules featuring the $-N=N-$ chromophore and extended conjugated systems. This structural characteristic grants them diverse applications in various fields, including radical reaction initiators, organic dyes, photosensitive materials, pigments, and indicators. Additionally, aromatic azo compounds serve as crucial intermediates in numerous organic conversion processes.^{1–4} Traditional methods for synthesizing aromatic azo compounds typically involve diazonium coupling or Mills reaction. The diazonium coupling reaction offers advantages such as rapid reaction rates and high yields. However, it imposes significant limitations on the types of substituents allowed on the aromatic rings, thereby restricting the substrate scope. The Mills reaction typically requires acetic acid as a catalyst and involves nitroso aromatic compounds and primary aromatic amines as starting materials. However, the instability of nitroso compounds often leads to side reactions. Over the past decade, significant efforts have been made to develop new catalytic methods for synthesizing aromatic azo

compounds through the direct oxidative coupling of anilines.^{1,5–7}

Transition metal catalysts⁸ offer a promising option for industrial-scale production of azo compounds due to their low cost and high efficiency.^{9,10} Furthermore, various strategies, including element doping, structural recombination, crystal plane orientation growth and morphology regulation, can be employed to optimize these catalysts for azo compounds synthesis.^{11,12} Metal nanoparticles and metal supported nanoparticles effectively used for azo compounds synthesis.² To enhance catalytic efficiency, researchers have developed sophisticated design strategies for metal nano particles, focusing on controlling particle size and shape, modifying electronic properties, and optimizing metal-support interactions.^{13,14} The support material significantly influences the catalytic performance of metal nanoparticles for azo compounds synthesis, particularly at the metal-support interface where active sites are located.⁴ However, these active sites are relatively few, limiting overall catalytic activity. Furthermore, the metal-support interaction can weaken during reactions, leading to aggregation of active metal species and reduced performance.¹²

Research has shown that incorporating alkali metals into catalysts can significantly enhance their electron transfer properties, leading to improved catalytic conversion of aromatic amines into azo compounds.¹⁵ Alkali metals offer advantages over transition metals, including higher charge density, stronger bonding with functional groups, and being lightweight

^aSchool of Chemical and Environmental Engineering, Anhui Polytechnic University, Wuhu, 241000, China. E-mail: xdy826@ahpu.edu.cn

^bDepartment of Chemistry, College of Science, King Faisal University, Hofuf, Eastern Province AlAhsa-31982, Kingdom of Saudi Arabia. E-mail: fshah@kfu.edu.sa

^cSchool of Chemistry and Environmental Science, Shangrao Normal University, Shangrao, 334000, China. E-mail: chemweihua419818@sina.com


and non-toxic. These benefits make alkali metal incorporation an attractive approach for enhancing catalytic performance.¹⁶

Gold catalysts have recently gained significant attention in organic synthesis due to their versatility and effectiveness. Recent studies, particularly those focusing on gold-support interactions, have enabled practical applications of gold catalysts.⁶ Notably, Grirrane *et al.*⁶ reported that Au/TiO₂ and Au/CeO₂ nanocatalysts demonstrated high conversion and selectivity for aniline to azo compound synthesis using O₂ as the oxidant. Zhu *et al.*¹² demonstrated the use of Au/ZrO₂ catalyst in a photocatalytic reaction, achieving high conversion of nitro compounds under atmospheric pressure. Research has shown that the performance of gold catalysts can be enhanced by selecting suitable supports and controlling gold nanoparticle size. Despite this progress, achieving both high conversion and high selectivity in the oxidation of aniline to azoxy compounds remains a significant challenge in supported metal catalysis systems. Li *et al.*¹⁷ found that modifying ZrO₂ with Fe altered its crystal structure and increased the number of surface acidic and basic sites, enhancing the activation of methanol and CO₂. Similarly, introducing Fe into Cu-based catalysts for dimethyl carbonate formation improved catalytic activity due to a balanced distribution of acidic and basic sites, attributed to the combined effects of metallic Cu, Fe species, and oxygen-deficient Fe₂O₃.

2 Methods of synthesis of azo compounds

2.1. Direct oxidation of aromatic amines and their derivatives

The direct oxidation of aromatic amines to azo compounds is a promising and environmentally friendly method. Oxygen is the ideal oxidant due to its green and atomically economical nature. However, oxygen molecules typically require catalytic activation to participate in the reaction, limiting their direct use. Transition metal compounds have gained attention for variable oxidation states and redox potentials, enabling catalytic activity. Additionally, these catalysts can be regenerated using oxygen from the air, making the process more

sustainable. Dutta *et al.*¹⁸ devised an economical approach for synthesizing aromatic azo compounds, employing a mesoporous manganese oxide catalyst with air serving as the oxidant. This approach enabled the formation of diverse unsymmetrical and symmetrical azo compounds from aniline derivatives under mild atmospheric conditions, with moderate to excellent yields. The catalyst showed good reusability, making the protocol promising for practical applications. They assumed that the radical species **3a** formed from aniline (**1a**) was coupling with another molecule of aniline **1a** to form **4** (a compound with a 3e⁻ σ bond), which through the successive loss of a proton, an electron, and another proton formed intermediate **6**. Intermediate **6** goes through all the aforementioned steps once again to provide the final product **Iaa**¹⁸ (Fig. 1).

The widespread use of solvents in organic synthesis contributes to environmental issues, making solvent-free reactions a desirable goal. Researchers have developed a method using copper acetate and a trace amount of palladium salt enables the efficient conversion of anilines to aromatic azo compounds under base- and solvent-free conditions. This approach also achieved satisfactory yields in cross-coupling reactions.¹⁹ Copper played a fundamental role in the catalytic process, aided by palladium salt and oxygen. This method offers a new way for synthesizing asymmetric and symmetric azo compounds and highlights the potential of transition metal compounds in catalysis (Fig. 2).

Maier *et al.*²⁰ developed a new method for synthesizing cyclic azo benzenes from diarylamine precursors, overcoming challenges related to steric hindrance and angular tension. The reaction utilized *m*-CPBA as the oxidant in a mixed solvent system of acetic acid and dichloromethane. The synthesis of cyclic azo-benzenes offers a new type of photo-molecular switch. However, the method has limitations, including reduced yields for diarylamines with strong electron-withdrawing or electron-donating groups, and the need for additional derivatization steps for amino-substituted diarylamines. Furthermore, the reaction can generate multiple by-products and shows limited substrate selectivity, with substituent electronic properties having a weak impact on product yields. Direct oxidation of aromatic amines to form azo compounds necessitates precise

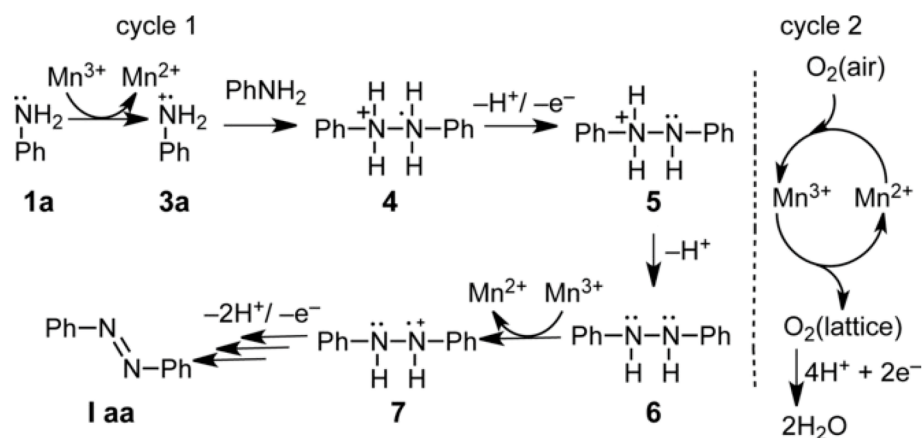


Fig. 1 Mesoporous manganese oxide catalyzed aerobic oxidative coupling of anilines to aromatic azo compounds.¹⁸



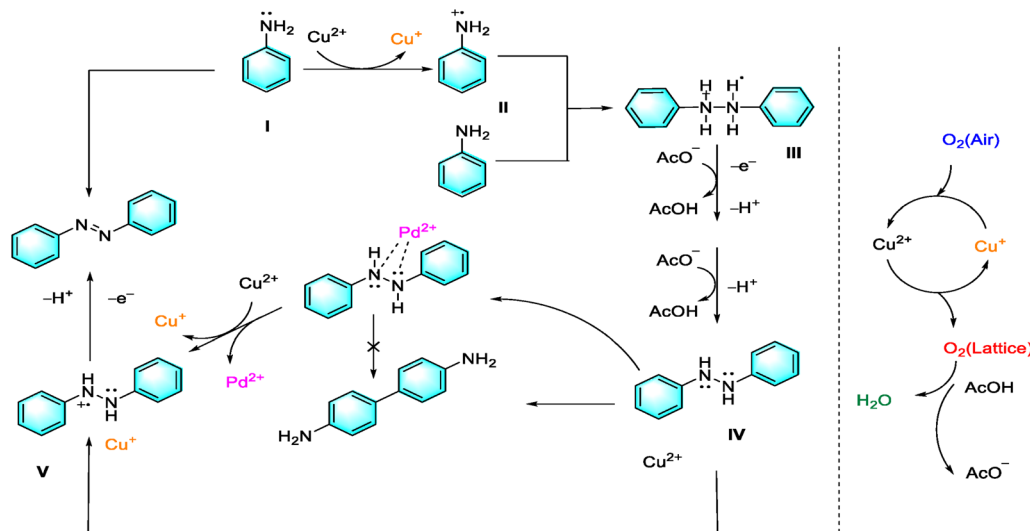


Fig. 2 Oxidation coupling of aniline to form azo compounds.¹⁹

control of the oxidation level to minimize the formation of by-products such as nitrobenzene and azobenzene oxide.

Shukla *et al.*²¹ developed a Cu–CeO₂ nanoparticle catalyst that achieved high yields and selectivity for azo compounds using H₂O₂ as the oxidant and acetonitrile as the solvent. Under optimized conditions, the catalyst delivered 95% aniline conversion and 92% azobenzene selectivity. Notably, the catalyst showed stability and heterogeneity, with minimal changes in Cu and Ce content after use. While significant progress has been made in synthesizing aromatic azo compounds, constructing heteroaromatic azo derivatives remains underexplored.

Jiang *et al.*²² introduced a novel method for synthesizing azo compounds through iodination of pyrazol-5-amine, utilizing *t*-butyl hydroperoxide (TBHP) as the oxidant and a copper salt as the catalyst. This approach enables the simultaneous formation of C–I and N–N bonds, followed by oxidative dehydrogenation to produce azopyrroles and iodo-substituted azopyrroles with diverse substituents. The reaction conditions are mild, and the catalytic system allows for selective modification of the pyrrole skeleton. However, the low yield in derivatization reactions needs optimization for practical applications. The direct oxidation of aromatic amines to synthesize azo compounds offers several advantages, but over-oxidation can lead to the formation of unwanted by-products.

2.2. Reductive coupling of aromatic nitro compound

Aromatic nitro compounds can be reduced to aromatic amines, making them a potential starting point for synthesizing azo compounds. A one-step synthesis from nitro compound to azo compound would enhance the economy and environmental sustainability of the reaction. This approach has gained significant attention in the scientific community.

Mondal *et al.*²³ developed a method to prepare Au nanoparticles using a nanoscale organic cage as a template, contributing to this area of research. The cage-immobilized Au

nanoparticles serve as a heterogeneous catalyst for selectively reducing nitroaromatics to azo compounds using 2-propanol, achieving high yields at room temperature. Under optimized conditions, 99% conversion to the corresponding azo compounds was obtained after 2 hours of UV irradiation in an inert atmosphere. Notably, no reaction occurred without Au nanoparticles, highlighting their crucial role in the process.

Yan *et al.*²⁴ developed a method where Pd(OAc)₂ was reduced *in situ* by NaBH₄ to form ultra-fine Pd nanoclusters (PdNCs), which were stabilized by nitroaromatics and dispersed in solvent. These PdNCs catalyzed the selective reduction of nitroarenes to various products with high yields, including those with electron-donating and electron-withdrawing groups. The protocol also worked well for nitro-fused aromatic compounds like nitronaphthalene, achieving an 80% yield. However, the reaction's selectivity needs improvement due to the potential oxidation of hydroxylamine, which can lead to side reactions. Further optimization of reaction conditions is necessary.

Hexagonal boron nitride is a 2D material with thermal stability and low toxicity making it suitable for catalytic applications (Fig. 3). It provides a platform for metal nanoparticles, offering more reactive sites. Research has shown that h-BN can inhibit oxygen activation, allowing catalytic hydrogenation of nitrobenzene in air. In a reaction mechanism, KOH facilitates hydrogen transfer from isopropanol to the Au/h-BN surface, forming an activated H donor. The H donor binds to Au nanoparticles, creating H–Au, which plays a crucial role in the reduction process. The H–Au species can also release H₂, enabling a continuous cycle.²⁵

2.3. Photocatalytic method

Photocatalytic synthesis is a promising method in organic chemistry that utilizes light energy to drive reactions. It offers advantages such as fast reaction rates, high selectivity, mild conditions, and reduced energy consumption compared to

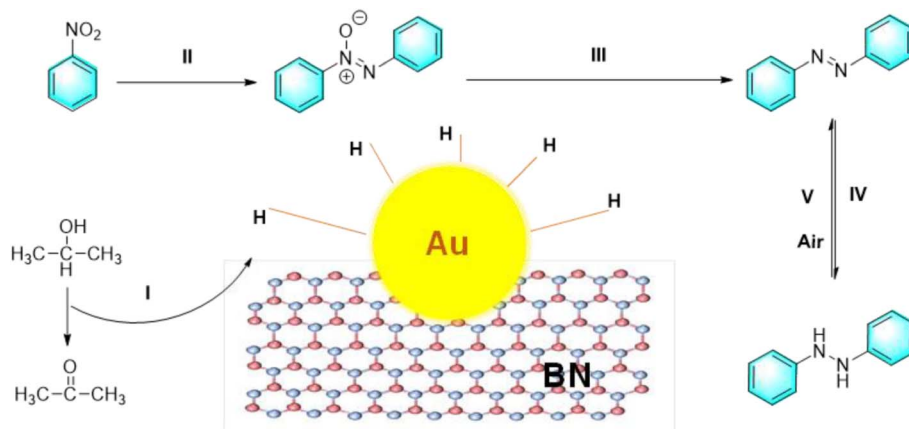


Fig. 3 The reduction of nitrobenzene catalyzed by Au/BN.²⁵

traditional methods. Zhou *et al.*²⁶ demonstrated that Pd nanoparticles loaded on mesoporous CdS (Pd@CdS) serve as a highly active and selective photocatalyst in water under visible light irradiation (Fig. 4). The composite catalyst Pd@CdS enables simultaneous photocatalytic conversion of glucose to arabinose and nitrosobenzene to azobenzene with high selectivity. Under visible light irradiation, photoexcited electrons are transferred from CdS to Pd nanoparticles, inhibiting electron-hole recombination and facilitating the reduction of nitrosobenzene to azobenzene. Meanwhile, glucose is oxidized by holes to form arabinose. The process is further enhanced by the interplay between the two reactions, where formic acid generated from glucose oxidation aids the hydrogenation of nitrobenzene, and nitrobenzene promotes glucose conversion by accepting electrons and H^+ ions.

Wang *et al.*²⁷ developed a CQDs-ZnIn₂S₄ nano-catalyst for the controlled catalytic hydrogenation of nitrobenzene under visible light. By adjusting the hydrogen source, and alkalinity the reaction can selectively produce azobenzene, azoxybenzene, or aniline. The mechanism involves ZnIn₂S₄ generating electrons and holes under light irradiation, with CQDs transferring electrons to facilitate the hydrogenation process. The addition of bases like NaOH promotes the formation of azobenzene or azoxybenzene. While photocatalytic synthesis offers many benefits, it still faces challenges like limited solar energy utilization, low quantum efficiency, and inadequate catalyst recyclability.

Rowshanpour *et al.*²⁸ reported the first instance of photo-catalytic Cu/photosensitizer synthesis of symmetric and non-symmetric azo compounds from readily available amines using renewable light energy input, ambient conditions, and ubiquitous air as a stoichiometric oxidant (Fig. 5).

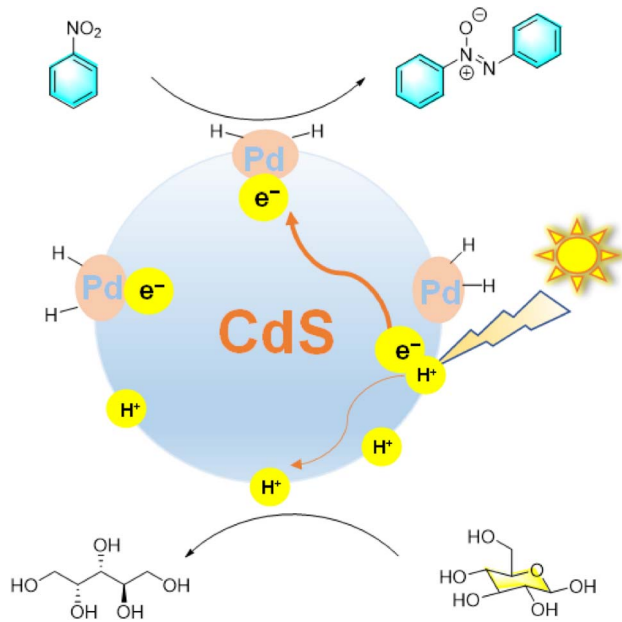


Fig. 4 Photochemical reduction of nitrobenzene catalyzed by Pd@CdS.²⁶

2.4. Aniline conversion by various catalytic materials

Lima *et al.*²⁹ reported the selective conversion of aniline to azoxybenzene at room temperature using amorphous niobium oxyhydroxide supported on δ -FeOOH. The catalysts were synthesized *via* a co-precipitation method by incorporating varying amounts of niobium oxyhydroxide into δ -FeOOH nanoparticles. This modification altered both the chemical and textural properties of δ -FeOOH, leading to a marked improvement in its catalytic efficiency for aniline oxidation in the presence of hydrogen peroxide. The catalytic activity and selectivity were influenced by the niobium content in the composite. The study examined the impact of various reaction parameters, such as solvent type, hydrogen peroxide volume, and reaction time. Among the tested catalysts, the one containing 10 wt% Nb exhibited the highest performance, achieving complete aniline conversion and 80.2% selectivity to azoxybenzene when propanol was used as the solvent at 25 °C. Additionally, this catalyst showed excellent stability and reusability, retaining its activity across multiple reaction cycles.

Jiang *et al.*¹⁹ developed a straightforward approach for synthesizing both symmetric and asymmetric aromatic azo



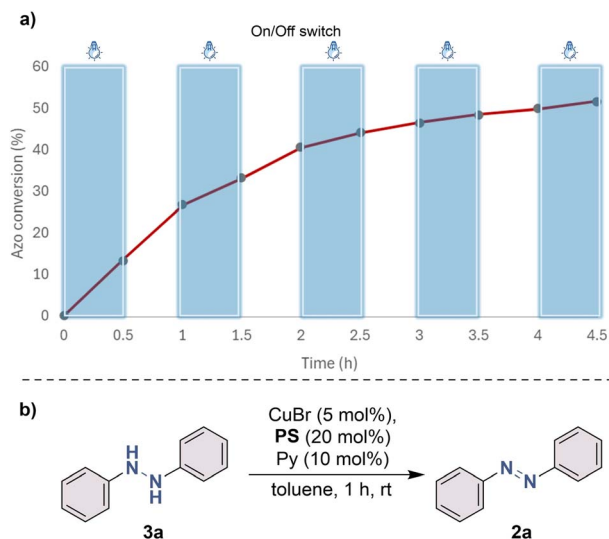


Fig. 5 (a) Light on/off experiment to track chain propagation. Blue columns represent the time period in which the light was on. The conversion data points were recorded using ^1H NMR in the span of 4.5 hours. (b) Reaction was run using hydrazine instead of aniline as the starting reagent in the absence of blue light.²⁸

compounds directly from anilines, employing $\text{Cu}(\text{OAc})_2$ as a catalyst under base-free and solvent-free conditions. The introduction of a small amount of palladium salt further enhanced the reaction yield. This approach also showed promise for cross-coupling nitridation reactions.

Wang *et al.*³⁰ developed a method for synthesizing azo-benzenes through the oxidative coupling of anilines using transition metal oxides, with manganese oxide OMS-2 showing the best activity and selectivity. They synthesized various symmetric and unsymmetric azo-benzenes with high conversion and selectivity rates. The selectivity of unsymmetric azo-benzenes was influenced by the difference in Hammett constants between the substituent groups. Research suggested that surface defect sites on the manganese oxide facilitate electron transfer and oxygen activation, proposing a single-electron transfer reaction mechanism based on detailed characterization.

Patel *et al.*³¹ reported a method using a polyoxometalate-based molecular molybdenum oxide catalyst to oxidize anilines to azobenzene and azoxybenzene compounds. This approach is compatible with a wide range of substrates and functional groups, allowing for the efficient synthesis of symmetric and asymmetric azo-benzenes and azoxybenzenes using H_2O_2 as a green oxidant. Mechanistic studies suggest the formation of highly active Mo imido complexes as intermediates.

Singh *et al.*³ developed a method for selectively oxidizing aromatic amines to azoxy derivatives using aluminum and gallium oxide nanorod catalysts. Gallium oxide nanorods, with their small size and high surface area, showed exceptional performance, achieving 94% aniline conversion with 98% selectivity to azoxybenzene. Notably, this reaction used hydrogen peroxide as a green oxidant and did not require

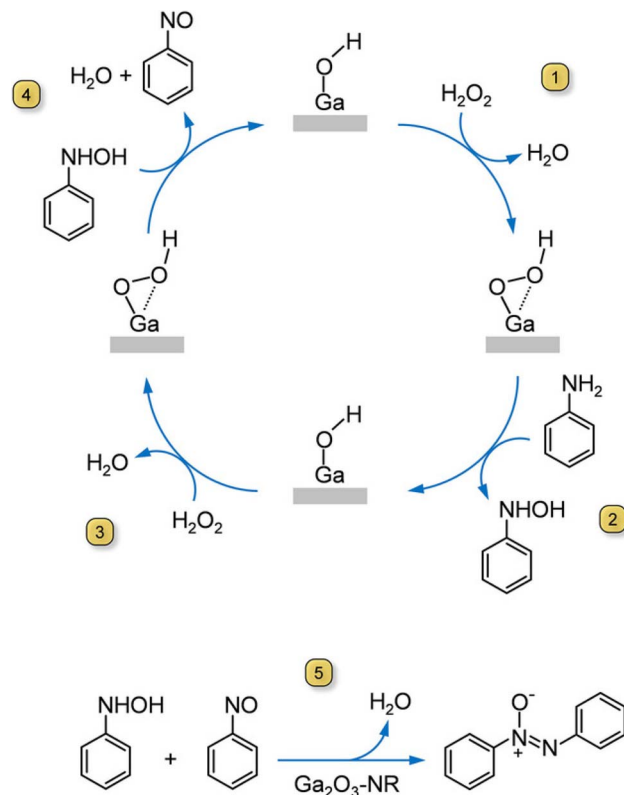


Fig. 6 Mechanism of aniline conversion to azo compounds over aluminium and gallium oxide catalysts at various conditions.³

transition metal catalysts. The catalyst also demonstrated excellent reusability, retaining its activity and selectivity over multiple runs. The detail mechanism is given in Fig. 6.

Patel *et al.*³¹ reported a direct oxidative azo coupling of anilines using a self-assembled, flower-like CuCo_2O_4 catalyst under aerobic conditions. The catalyst was synthesized *via* the oxalate decomposition method and characterized using raman spectroscopy, powder X-ray diffraction, transmission electron microscopy (TEM), field-emission scanning electron microscopy (FESEM), and energy-dispersive X-ray spectroscopy (EDX). The flower-like CuCo_2O_4 demonstrated excellent catalytic performance for the direct aerobic oxidative azo coupling of anilines under additive- and oxidant-free conditions. Density functional theory (DFT) calculations provided mechanistic insights, revealing that atmospheric oxygen preferentially adsorbs and dissociates at the Cu sites, while aniline dissociation occurs at the Co sites. This cooperative interaction between Cu and Co sites facilitates the selective activation of both oxygen and aniline during the reaction. The catalyst was recyclable and maintained high catalytic activity over at least eight consecutive cycles.

Shukla *et al.*²¹ reported the catalytic oxidation of aromatic amines to azoxy compounds using a Cu– CeO_2 catalyst and hydrogen peroxide (H_2O_2) as the oxidant. The catalyst was synthesized *via* a one-pot hydrothermal method employing cetyltrimethylammonium bromide (CTAB) as a surfactant, resulting in Cu nanoparticles supported on nanocrystalline CeO_2 . Characterization techniques including XRD, SEM, TEM,

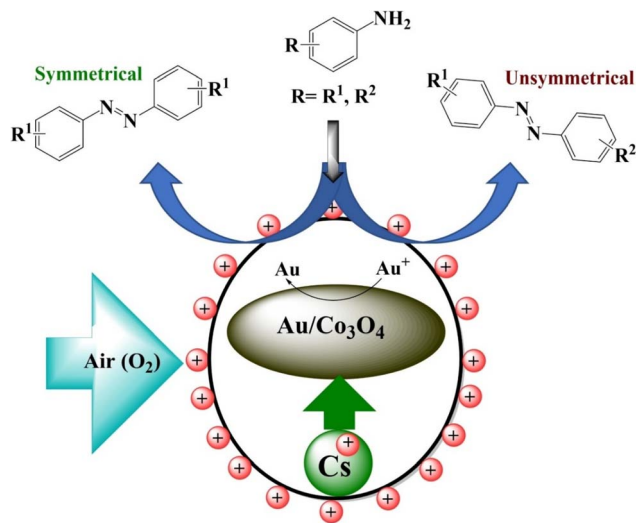


Fig. 7 Mechanism involved oxidation of aniline into symmetrical and unsymmetrical azo compounds.³²

XPS, TPR, EXAFS, BET surface area analysis, and UV-vis spectroscopy confirmed the successful formation and morphology of the catalyst. The catalyst exhibited excellent activity and selectivity for the oxidation of aromatic amines to their corresponding *N*-oxides. Optimal performance was observed with a Cu loading of 3.8 wt%, which yielded 5–10 nm Cu nanoparticles supported on 20–40 nm CeO_2 particles. At this loading, the catalyst achieved 95% aniline conversion and 92% selectivity for azoxybenzene. Higher Cu loadings led to agglomeration of Cu species, resulting in decreased catalytic efficiency. The study also systematically examined the influence of various reaction parameters, including temperature, reaction time, substrate type, and H_2O_2 molar ratio.

Oseghale *et al.*³² reported the development of a bifunctional Cs–Au/ Co_3O_4 catalyst, possessing both basic and redox properties, for the oxidative synthesis of aromatic azo compounds from anilines (Fig. 7). This eco-friendly, alkali-promoted catalyst enabled the oxidative dehydrogenative coupling of anilines to produce both symmetrical and unsymmetrical azo

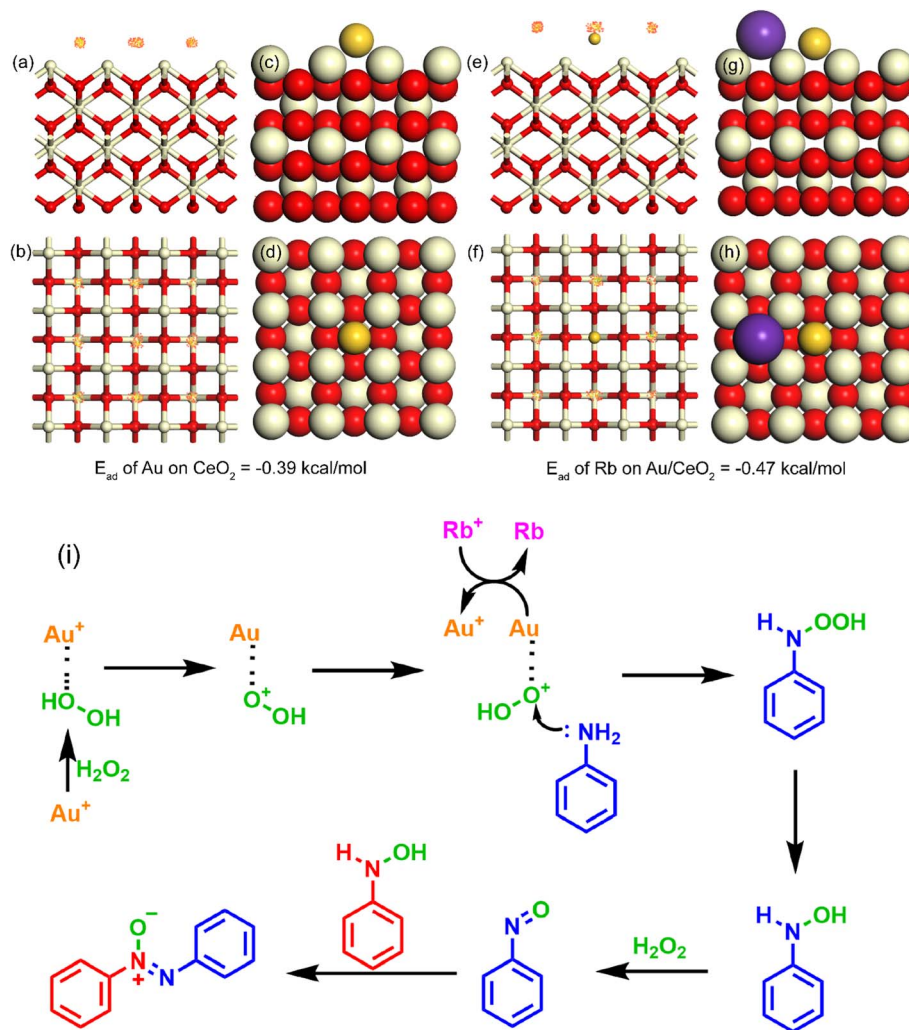


Fig. 8 (a) Side view of Au/CeO_2 (100) adsorption fields (b) top view of Au/CeO_2 (100) adsorption fields (c) side view and (d) top view of Au/CeO_2 (100) most stable adsorption site (e) side view and (f) top view of Rb doped Au/CeO_2 (100) adsorption fields (g) side view and (h) top view of Rb doped Au/CeO_2 (100) most stable adsorption site (i) proposed mechanism of the reaction.¹



Table 1 Comparison between activities of various reported catalysts at various conditions.¹

| Catalyst | Conversion (%) | Selectivity | Solvent | <i>T</i> (°C) | Time (h) | References |
|--|----------------|-------------|--------------------|---------------|----------|------------|
| 7.5% CuCeO ₂ | 82 | 72 | CH ₃ CN | 50 | 6 | 7 |
| Al ₂ O ₃ -nanopowder | 14 | 38 | EtOAc | 80 | 4 | 3 |
| Ga ₂ O ₃ -NR | 49 | 92 | EtOAc | 80 | 4 | 3 |
| Ag/Fe ₂ O ₃ nanocatalyst | 91 | 92 | CH ₃ CN | 50 | 8 | 33 |
| Nb ₂ O ₅ -scCO ₂ | 86 | 79 | EtOH | 25 | 1 | 34 |
| Nb-doped iron oxides | 33 | 59 | EtOH | 25 | 24 | 35 |
| Al ₂ O ₃ /AlNbO ₄ | 80 | 82.7 | DMF | 25 | 24 | 36 |

compounds using air as the oxidant, eliminating the need for base additives or toxic molecular oxygen. The catalyst demonstrated good reusability and operated efficiently under mild conditions. Enhanced catalytic performance was attributed to a higher concentration of basic sites, lower reduction in temperatures, and the active role of lattice oxygen in the nanostructure. The increased basicity promoted electron density on the active Au species, significantly boosting the yield of aromatic azo products.

Dutta *et al.*¹⁸ established a straightforward, economical, and mild catalytic method for synthesizing a broad spectrum of symmetrical and unsymmetrical aromatic azo compounds using inexpensive meso-MnO_x materials. A variety of aniline derivatives underwent both oxidative homocoupling and cross-coupling reactions, yielding products in moderate to excellent

yields (35–99%). The use of air as the terminal oxidant, the absence of precious metals or additives, operation under ambient conditions, and good catalyst reusability highlight the advantages of this system over existing methods. Mechanistic studies revealed the key roles of surface-active Mn³⁺ species, labile lattice oxygen, and radical intermediates in the reaction cycle. A manganese-mediated electron-transfer mechanism was proposed and supported by density functional theory (DFT) calculations. Further studies are ongoing to refine the mechanism and enhance reaction efficiency.

Khan *et al.*¹ reported the development of a Rb-doped Au/CeO₂ nanocatalyst that demonstrated exceptional efficiency for the selective oxidation of anilines to azocompounds using hydrogen peroxide as the oxidant. The catalyst achieved complete aniline conversion (100%) and remarkably high

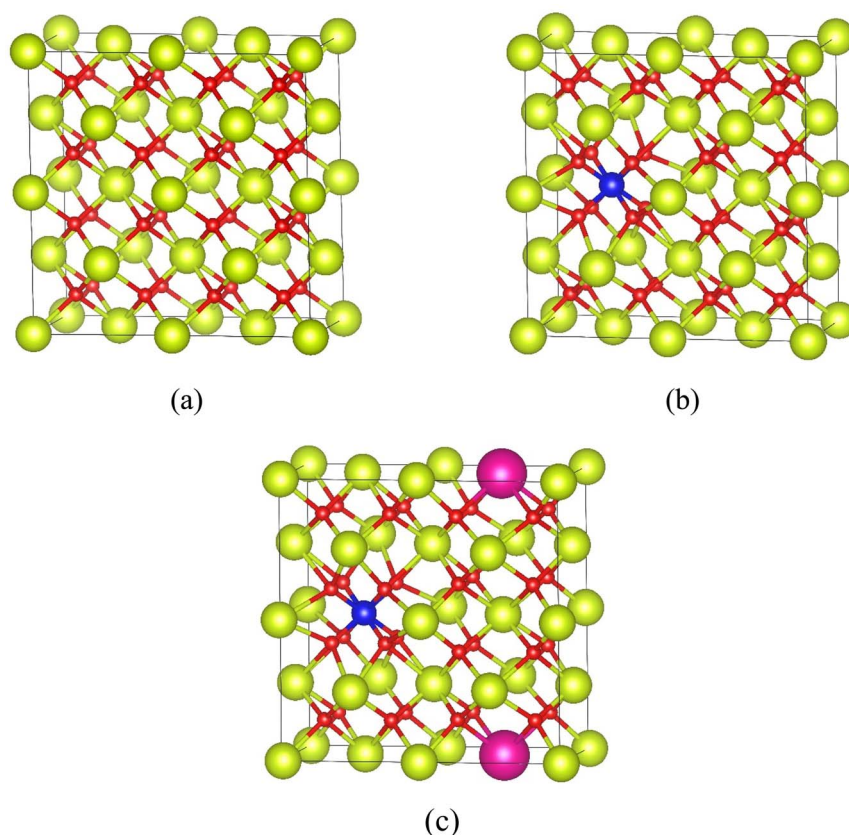


Fig. 9 Optimized structures of the CeO₂ (a), Fe/CeO₂ (b), Rb-Fe/CeO₂ (c) supercells. Red, yellow, blue, and fuchsia correspond to oxygen, cerium, iron, and rubidium atoms, respectively. The solid black line confines the supercell.²



selectivity (92%) toward azoxybenzene. The incorporation of Rb^+ was found to promote electron transfer, enhancing the formation of catalytically active Au^+ species. A DFT calculation is done to probe in the exact interaction mechanism of the catalyst surface and product produced (Fig. 8). Table 1 shows various catalytic activities at various conditions.

Khan *et al.*² also reported a Rb-promoted Fe/CeO₂ nanocatalyst to investigate the role of Rb as a promoter in enhancing the catalytic performance for the selective oxidation of aniline to azoxybenzene using H₂O₂ as the oxidant. The optimized catalyst, Rb-Fe/CeO₂, achieved complete aniline conversion (100%) with 91% selectivity toward azoxybenzene. The incorporation of Rb significantly improved the catalyst's electron transfer capability, reduced activation energy, and induced lattice distortion, leading to the formation of oxygen vacancies and Ce³⁺ species key contributors to the enhanced catalytic activity. Additionally, Rb modification helped suppress strong Brønsted acid sites, stabilized the Fe/CeO₂ structure, improved Fe dispersion, and created an electron-rich environment that facilitated substrate activation. These synergistic effects increased the basic strength and electron density of the active Fe species, compensating for their inherent electronic limitations and resulting in improved catalytic efficiency. Reaction parameters such as catalyst loading (20–100 mg), reaction time (2–24 h), temperature (25–100 °C), solvent type, and volume (0.5–2 mL) were systematically studied in a 50 mL round-bottom flask with reflux conditions. DFT calculation (Fig. 9) has been done to determine interactions between substrate and catalyst surface.²

3 Conclusions

In conclusion, this comprehensive review highlights the significant advancements and challenges in the catalytic conversion of aniline into azo compounds. The development of efficient and sustainable catalytic systems has shown great promise in improving product yields, selectivity, and reducing environmental impact. Various catalysts, including homogeneous and heterogeneous systems, have been explored, and their mechanisms and performance have been discussed. Despite the progress made, further research is needed to overcome the existing limitations, such as catalyst stability and recyclability. Future studies should focus on designing novel catalysts, developing solvent-free protocols and methods that fully integrate green oxidants, optimizing reaction conditions, and investigating the underlying mechanisms to achieve more efficient and environmentally friendly processes. This review provides a foundation for researchers and industry professionals to advance the field of catalytic aniline conversion and develop sustainable methods for producing valuable azo compounds.

Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Conflicts of interest

The authors declare no competing financial interest.

Data availability

Data is available on request.

Funding

This work was supported by the Deanship of Scientific Research, Vice Presidency for Graduate Studies and Scientific Research, King Faisal University, Saudi Arabia [grant no. KFU252772].

References

- 1 A. Khan, P. Ju, Z. Han, Y. Xie, Z. Gan, H. Zhong, Z. He and W. Xie, Rb-Promoted Au/CeO₂ Nanocatalyst for Remarkably-Enhanced Aniline Conversion to Azoxybenzene with Ultrahigh Selectivity, *ChemCatChem*, 2024, **16**, e202400289.
- 2 A. Khan, S. Xiao, Y. Xie, S. Kaya, S. Zareen, N. Muhammad, K. Parveen and D. Xu, Rb-promoted Fe/CeO₂ nanocatalyst for aniline conversion into azoxybenzene, DFT calculations and mechanism, *New J. Chem.*, 2025, **49**, 921–934.
- 3 B. Singh, D. Mandelli and P. P. Pescarmona, Efficient and selective oxidation of aromatic amines to azoxy derivatives over aluminium and gallium oxide catalysts with nanorod morphology, *ChemCatChem*, 2020, **12**, 593–601.
- 4 Z. R. Al-Majidi, W. H. Al-Dahhan, M. S. Shihab and M. H. Nazari, Azo Compounds and their Potential Applications: Article Review, *J. Pure Sci.*, 2025, **9**, 144–163.
- 5 Y. Tao, B. Singh, V. Jindal, Z. Tang and P. P. Pescarmona, Niobium oxide prepared through a novel supercritical-CO₂-assisted method as a highly active heterogeneous catalyst for the synthesis of azoxybenzene from aniline, *Green Chem.*, 2019, **21**, 5852.
- 6 A. Grirrane, A. Corma and H. García, Gold-catalyzed synthesis of aromatic azo compounds from anilines and nitroaromatics, *Science*, 2008, **322**, 1661–1664.
- 7 S. S. Acharyya, S. Ghosh and R. Bal, Catalytic oxidation of aniline to azoxybenzene over CuCr₂O₄ spinel nanoparticle catalyst, *ACS Sustain. Chem. Eng.*, 2014, **2**, 584–589.
- 8 M. Kamrojjaman, A. Nath, R. Jahan, M. A. Bhuiyan, S. U. Siyam and M. A. Ali, Synthesis, characterization and mechanistic studies of an activated carbon-supported nickel (Ni/C) catalyst for the effective amidation of aldehydes, *RSC Adv.*, 2025, **15**, 18108–18113.
- 9 L. Luo, Y. Liu, W. Chen, X. Xue, S.-M. Xu, M. Li, H. Zhou, L. Ma, M. Xu and X. Kong, Photoelectrocatalytic synthesis of aromatic azo compounds over porous nanoarrays of bismuth vanadate, *Chem Catal.*, 2023, **3**, 1–14.
- 10 S. Saki, M. Tavakolian and M. Hosseini-Sarvari, Selective Photocatalytic Reduction of Nitrobenzene to Anilines, Azoxybenzene, and Azobenzene: A Solvent-Dependent and



- Light-Induced Process Mediated by CdS/NH₂-MIL-125 Nanocomposite, *Org. Biomol. Chem.*, 2025, 6625–6636.
- 11 X. Mei, X. Zhao, Y. Chen, B. Deng, Q. Geng, Y. Cao, Y. Li and F. Dong, Highly efficient H₂O₂ production via two-electron electrochemical oxygen reduction over Fe-doped CeO₂, *ACS Sustain. Chem. Eng.*, 2023, **11**, 15609–15619.
 - 12 H. Zhu, X. Ke, X. Yang, S. Sarina and H. Liu, Reduction of nitroaromatic compounds on supported gold nanoparticles by visible and ultraviolet light, *Angew. Chem., Int. Ed.*, 2010, **49**, 9657–9661.
 - 13 I. Ahmad, M. K. Abosoda, Y. Jadeja, G. Sangwan, V. Kavitha, A. Kashyap, S. Homurotova, M. Kazemi and R. Javahershenas, A Comprehensive Review on Carbonylation Reactions: Catalysis by Magnetic Nanoparticles Supported Transition Metals, *Nanoscale Adv.*, 2025, 3189–3209.
 - 14 H. Van Ngoc and T. Q. Trang, Investigation of C and Si-doped 2D germanene quantum dots for potential nanotechnology applications, *RSC Adv.*, 2025, **15**, 19192.
 - 15 M. C. Ribeiro, G. Jacobs, B. H. Davis, D. C. Cronauer, A. J. Kropf and C. L. Marshall, Fischer–Tropsch synthesis: an in-situ TPR-EXAFS/XANES investigation of the influence of Group I alkali promoters on the local atomic and electronic structure of carburized iron/silica catalysts, *J. Phys. Chem. C*, 2010, **114**, 7895–7903.
 - 16 B. Liang, H. Duan, T. Sun, J. Ma, X. Liu, J. Xu, X. Su, Y. Huang and T. Zhang, Effect of Na promoter on Fe-based catalyst for CO₂ hydrogenation to alkenes, *ACS Sustain. Chem. Eng.*, 2018, **7**, 925–932.
 - 17 A. Li, Y. Pu, F. Li, J. Luo, N. Zhao and F. Xiao, Synthesis of dimethyl carbonate from methanol and CO₂ over Fe–Zr mixed oxides, *J. CO₂ Util.*, 2017, **19**, 33–39.
 - 18 B. Dutta, S. Biswas, V. Sharma, N. O. Savage, S. P. Alpay and S. L. Suib, Mesoporous manganese oxide catalyzed aerobic oxidative coupling of anilines to aromatic azo compounds, *Angew. Chem.*, 2016, **128**, 2211–2215.
 - 19 B. Jiang, Y.-Y. Du and G.-Z. Han, Palladium-mediated base-free and solvent-free synthesis of aromatic azo compounds from anilines catalyzed by copper acetate, *Green Process. Synth.*, 2022, **11**, 823–829.
 - 20 M. S. Maier, K. Hüll, M. Reynnders, B. S. Matsuura, P. Leippe, T. Ko, L. Schäffer and D. Trauner, Oxidative approach enables efficient access to cyclic azobenzenes, *J. Am. Chem. Soc.*, 2019, **141**, 17295–17304.
 - 21 A. Shukla, R. K. Singha, L. S. Konathala, T. Sasaki and R. Bal, Catalytic oxidation of aromatic amines to azoxy compounds over a Cu–CeO₂ catalyst using H₂O₂ as an oxidant, *RSC Adv.*, 2016, **6**, 22812–22820.
 - 22 B. Jiang, Y. Ning, W. Fan, S.-J. Tu and G. Li, Oxidative dehydrogenative couplings of pyrazol-5-amines selectively forming azopyrroles, *J. Org. Chem.*, 2014, **79**, 4018–4024.
 - 23 B. Mondal and P. S. Mukherjee, Cage encapsulated gold nanoparticles as heterogeneous photocatalyst for facile and selective reduction of nitroarenes to azo compounds, *J. Am. Chem. Soc.*, 2018, **140**, 12592–12601.
 - 24 Z. Yan, X. Xie, Q. Song, F. Ma, X. Sui, Z. Huo and M. Ma, Tandem selective reduction of nitroarenes catalyzed by palladium nanoclusters, *Green Chem.*, 2020, **22**, 1301–1307.
 - 25 Q. Liu, Y. Xu, X. Qiu, C. Huang and M. Liu, Chemoselective hydrogenation of nitrobenzenes activated with tuned Au/h-BN, *J. Catal.*, 2019, **370**, 55–60.
 - 26 B. Zhou, J. Song, T. Wu, H. Liu, C. Xie, G. Yang and B. Han, Simultaneous and selective transformation of glucose to arabinose and nitrosobenzene to azoxybenzene driven by visible-light, *Green Chem.*, 2016, **18**, 3852–3857.
 - 27 B. Wang, Z. Deng and Z. Li, Efficient chemoselective hydrogenation of nitrobenzene to aniline, azoxybenzene and azobenzene over CQDs/ZnIn₂S₄ nanocomposites under visible light, *J. Catal.*, 2020, **389**, 241–246.
 - 28 R. Rowshanpour, S. Vemulapalli and T. Dudding, A Photo-Dual Catalytic Strategy for Azo Compound Synthesis, *Adv. Synth. Catal.*, 2025, e202500008.
 - 29 A. L. Lima, D. C. Batalha, H. V. Fajardo, J. L. Rodrigues, M. C. Pereira and A. C. Silva, Room temperature selective conversion of aniline to azoxybenzene over an amorphous niobium oxyhydroxide supported on δ-FeOOH, *Catal. Today*, 2020, **344**, 118–123.
 - 30 M. Wang, J. Ma, M. Yu, Z. Zhang and F. Wang, Oxidative coupling of anilines to azobenzenes using heterogeneous manganese oxide catalysts, *Catal. Sci. Technol.*, 2016, **6**, 1940–1945.
 - 31 A. R. Patel, G. Patel, G. Maity, S. P. Patel, S. Bhattacharya, A. Putta and S. Banerjee, Direct oxidative azo coupling of anilines using a self-assembled flower-like CuCo₂O₄ material as a catalyst under aerobic conditions, *ACS Omega*, 2020, **5**, 30416–30424.
 - 32 C. O. Oseghale, D. P. Fapojuwo, O. A. Alimi, C. A. Akinawo, B. M. Mogudi, O. R. Onisuru and R. Meijboom, Bifunctional Cs-Au/Co₃O₄ (Basic and Redox)-Catalyzed Oxidative Synthesis of Aromatic Azo Compounds from Anilines, *Eur. J. Org. Chem.*, 2021, **2021**, 5063–5073.
 - 33 B. Paul, S. K. Sharma, S. Adak, R. Khatun, G. Singh, D. Das, V. Joshi, S. Bhandari, S. S. Dhar and R. Bal, Low-temperature catalytic oxidation of aniline to azoxybenzene over an Ag/Fe₂O₃ nanoparticle catalyst using H₂O₂ as an oxidant, *New J. Chem.*, 2019, **43**, 8911–8918.
 - 34 Y. Tao, B. Singh, V. Jindal, Z. Tang and P. P. Pescarmona, Niobium oxide prepared through a novel supercritical-CO₂-assisted method as a highly active heterogeneous catalyst for the synthesis of azoxybenzene from aniline, *Green Chem.*, 2019, **21**, 5852–5864.
 - 35 A. L. Lima, H. V. Fajardo, A. E. Nogueira, M. C. Pereira, L. C. Oliveira, J. P. de Mesquita and A. C. Silva, Selective oxidation of aniline into azoxybenzene catalyzed by Nb-peroxo@ iron oxides at room temperature, *New J. Chem.*, 2020, **44**, 8710–8717.
 - 36 D. C. Batalha, S. C. Luz, J. G. Taylor, H. V. Fajardo, B. S. Noremborg, I. J. Cherubin, R. M. Silva, M. R. Gonçalves, C. P. Bergmann and A. Valentini, Application of Al₂O₃/AlNbO₄ in the oxidation of aniline to azoxybenzene, *Chem. Pap.*, 2020, **74**, 543–553.

