

Cite this: *Chem. Sci.*, 2025, 16, 6845

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Atomic-level engineering of single Ag<sup>1+</sup> site distribution on titanium–oxo cluster surfaces to boost CO<sub>2</sub> electroreduction†

Ru-Xin Meng,<sup>‡a</sup> Lan-Cheng Zhao,<sup>‡b</sup> Li-Pan Luo,<sup>c</sup> Yi-Qi Tian,<sup>a</sup> Yong-Liang Shao,<sup>d</sup> Qing Tang,<sup>Ⓜ\*c</sup> Likai Wang,<sup>Ⓜ\*b</sup> Jun Yan<sup>Ⓜa</sup> and Chao Liu<sup>Ⓜ\*a</sup>

Precise control over the distribution of active metal sites on catalyst surfaces is essential for maximizing catalytic efficiency. Addressing the limitations of traditional cluster catalysts with core-embedded catalytic sites, this work presents a strategy to position catalytic sites on the surfaces of oxide clusters. We utilize a calixarene-stabilized titanium–oxo cluster (Ti<sub>12</sub>L<sub>6</sub>) as a scaffold to anchor Ag<sup>1+</sup> *in situ*, forming the unique nanocluster Ti<sub>12</sub>Ag<sub>4.5</sub> with six surface-exposed Ag<sup>1+</sup> sites. The *in situ* transformation from Ti<sub>12</sub>L<sub>6</sub> into Ti<sub>12</sub>Ag<sub>4.5</sub> clusters was traced through mass spectrometry, revealing a solvent-mediated dynamic process of disintegration and reassembly of the Ti<sub>12</sub>L<sub>6</sub> macrocycle. The unique Ti<sub>12</sub>Ag<sub>4.5</sub> cluster, featuring a surface-exposed catalytic site configuration, efficiently catalyzes the electroreduction of CO<sub>2</sub> to CO over a broad potential window, achieving CO faradaic efficiencies exceeding 82.0% between –0.4 V and –1.8 V. Its catalytic performance surpasses that of bimetallic Ti<sub>2</sub>Ag<sub>2</sub>, which features a more conventional design with Ag<sup>1+</sup> sites embedded within the cluster. Theoretical calculations indicate that the synergy between the titanium–oxo support and the single Ag<sup>1+</sup> sites lowers the activation energy, facilitating the formation of the \*COOH intermediate. This work reveals that engineered interactions between active surface metal and the oxide support could amplify catalytic activity, potentially defining a new paradigm in catalyst design.

Received 23rd October 2024  
Accepted 6th January 2025

DOI: 10.1039/d4sc07186g

rsc.li/chemical-science

## Introduction

Within the intricate sphere of catalysis, the sophisticated interplay of size, morphology, and structural attributes of materials is recognized for its profound influence on catalytic efficacy.<sup>1–4</sup> Recently developed single-atom catalysts (SACs), with isolated metal atoms dispersed on solid supports, are garnering significant attention due to their exceptional catalytic efficiency and ability to maximize the utilization of metal atoms.<sup>5–9</sup> Oxide-supported SACs, in particular, are among the most thoroughly investigated systems.<sup>10</sup> Advances in the fabrication of these materials are noteworthy, but achieving uniform dispersion of

catalytic sites on oxide substrates remains a significant challenge.<sup>11</sup> This requires not only advanced synthesis techniques but also sophisticated characterization methods.<sup>12</sup> The complexity is further exacerbated by the absence of detailed atomic structures, which obscures the analysis of the metal coordination environment—a pivotal factor in determining the performance of these catalyst systems.<sup>13–15</sup>

To effectively tackle these challenges, it is crucial to develop molecular analogues for oxide-supported single-atom materials. Recent advances in TiO<sub>2</sub> analogues,<sup>16–19</sup> particularly through the development of crystalline titanium oxide clusters (TOCs), have facilitated comprehensive investigations of TiO<sub>2</sub> structures and reactivities at the molecular level.<sup>20–24</sup> These TOCs, when modified with catalytically active single metals, hold promise as effective molecular mimics for oxide-supported SACs. However, heterometal-doped TOCs are typically created *via* a one-pot solvothermal method, with heterometal sites embedded deep within the cluster core, often in fully coordinated states.<sup>25–29</sup> Such configurations limit the interactions with reactants, exposing a significant shortfall in their capacity to act as true molecular proxies. This insight highlights the urgent need for a new class of crystalline, cluster-stabilized single-atom materials, designed to more precisely emulate the structural and reactive properties of oxide-supported SACs at a molecular level.<sup>30,31</sup>

<sup>a</sup>College of Chemistry and Chemical Engineering, Central South University, Changsha 410083, Hunan, P. R. China. E-mail: chaoliu@csu.edu.cn

<sup>b</sup>School of Chemistry and Chemical Engineering, Shandong University of Technology, Zibo 255049, Shandong, P. R. China. E-mail: lkwangchem@sdut.edu.cn

<sup>c</sup>College of Chemistry and Chemical Engineering, Chongqing University, Chongqing, 400044, P. R. China. E-mail: qingtang@cqu.edu.cn

<sup>d</sup>School of Chemistry and Chemical Engineering, Lanzhou University, Lanzhou, 730000, P. R. China

† Electronic supplementary information (ESI) available: X-ray crystallographic file in CIF format, and full experimental and computational details. CCDC 2349621–2349625. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d4sc07186g>

‡ These authors contributed equally.




Here, we present an approach designed to strategically place catalytic  $\text{Ag}^{1+}$  sites on the surfaces of oxide clusters (Scheme 1). Employing thiacalix[4]arene (TC4A) as a protective ligand,<sup>32–38</sup> we meticulously engineered a titanium–oxo macrocycle,  $\text{Ti}_{12}\text{L}_6$ , through a one-step solvothermal method, which is enriched with surface O and S sites. We utilized  $\text{Ti}_{12}\text{L}_6$  as a scaffold for the *in situ* loading of  $\text{Ag}^{1+}$  ions, revealing a solvent-mediated assembly process through mass spectrometry. In *N,N*-dimethylformamide (DMF) solution, the scaffold undergoes decomposition under the cleavage of  $\text{Ag}^{1+}$  ions; however, in acetonitrile, the scaffold remains stable and coordinates six accessible single  $\text{Ag}^{1+}$  sites on the cluster surface, ultimately transforming into a  $\text{Ti}_{12}\text{Ag}_{4.5}$  cluster.  $\text{Ti}_{12}\text{Ag}_{4.5}$  has proven to be an exceptional catalyst for the electrochemical reduction of  $\text{CO}_2$ , exhibiting superior reactivity and CO selectivity compared to its bimetallic counterpart,  $\text{Ti}_2\text{Ag}_2$ , which possesses a more conventional structure with  $\text{Ag}^{1+}$  sites embedded within the cluster matrix. Notably,  $\text{Ti}_{12}\text{Ag}_{4.5}$  exhibits high selectivity for CO across a wide voltage range, with CO faradaic efficiency ( $\text{FE}_{\text{CO}}$ ) consistently exceeding 82.0% from  $-0.4$  V to  $-1.8$  V vs. RHE, reaching a peak  $\text{FE}_{\text{CO}}$  of 92.7%. At an overpotential of  $\sim -1.4$  V, the system remained stable for continuous electrolysis over 11 h with a CO partial current density exceeding  $100.0$  mA  $\text{cm}^{-2}$ , while the  $\text{FE}_{\text{CO}}$  consistently remains above 85.0%. We elucidated the reaction path using *in situ* ATR-SEIRAS technology and comprehensively calculated the Gibbs free energy changes for each elementary step of  $\text{CO}_2$  conversion to CO, highlighting the critical contribution of exposed Ag centers to the observed catalytic prowess.

## Results and discussion

### One-step synthesis of titanium–oxo macrocyclic carriers

The synthetic route commenced with the reaction of  $\text{Ti}(\text{O}^i\text{Pr})_4$  with TC4A in a solvent blend of  $\text{CH}_3\text{CN}/\text{CHCl}_3$ , maintained at  $80$  °C for three days. This process yielded a turbid yellow liquid. Extending the reaction duration by introducing acetone and continuing incubation at  $80$  °C for an additional three days led to the crystallization of yellow rhomboid crystals of  $\text{Ti}_{12}\text{L}_6$ . Interestingly, this reaction exhibits a high sensitivity to temperature changes. Upon heating to  $130$  °C, certain sulfur sites in TC4A oxidize, leading to the emergence of two distinct

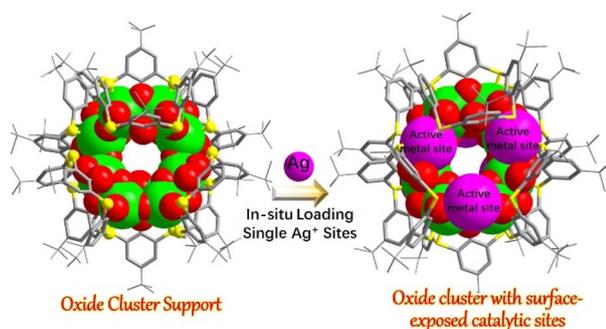

Scheme 1 Schematic representation of the cluster assembly featuring a Ti–oxo core with surface-exposed  $\text{Ag}^{1+}$  catalytic sites.

TOCs,  $\text{Ti}_8\text{L}_6$  and  $\text{Ti}_8\text{L}_5$ . SCXRD analysis revealed that the  $\text{Ti}_{12}\text{L}_6$  cluster has the composition of  $\{\text{H}_6\text{Ti}_{12}\text{O}_{18}(\text{HTC4A})_6\}$ , featuring a core–shell architecture where a central Ti–oxo macrocycle is encapsulated by six TC4A molecules.  $\text{Ti}_{12}\text{L}_6$  consists of six  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  units interconnected by twelve  $\mu_2\text{-O}^{2-}$  (Fig. 1A). TC4A adopts a mono-cone configuration, coordinating with two  $\text{Ti}^{4+}$  through three phenoxide groups and two S atoms, thereby forming the  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  units. These units are geometrically arranged in a triangular pattern, bridged by five  $\mu_2\text{-O}$  linkages to form a trimeric  $\{\text{Ti}_6(\text{TC4A})_3\}$ . This trimer further aggregates into the hexameric  $\{\text{Ti}_{12}(\text{TC4A})_6\}$  structure *via* the integration of two additional  $\mu_2\text{-O}^{2-}$  ions (Fig. 1B). This configuration yields a “donut” shape with an outer diameter of 3 nm, representing the largest TC4A-stabilized TOC reported to date (Fig. 1C). The structure of  $\text{Ti}_8\text{L}_6$  closely resembles that of  $\text{Ti}_{12}\text{L}_6$ , with a central  $\text{Ti}_8\text{O}_8$  ring encircled by six TC4A molecules (Fig. 1D). In contrast, the core of  $\text{Ti}_8\text{L}_5$  consists of a  $\text{Ti}_8\text{O}_{10}$  cluster, surrounded by five TC4A molecules arranged in a pentagonal bipyramidal configuration. In both structures, some of the TC4A molecules undergo oxidation, with one or two sulfur sites being converted to  $\text{S}=\text{O}$  groups. Additionally, each structure has two  $\text{Na}^+$  ions adsorbed on its surface.

### Solvent-mediated assembly of $\text{Ti}_{12}\text{Ag}_{4.5}$ clusters

The surfaces of this series of calixarene-stabilized TOCs are endowed with abundant O/S sites. Specifically, in  $\text{Ti}_8\text{L}_6$  and  $\text{Ti}_8\text{L}_5$ , these sites facilitate the adsorption of  $\text{Na}^+$  onto the cluster surfaces. This characteristic has inspired us to utilize these clusters as carriers for positioning  $\text{Ag}^{1+}$  ions. In our preliminary studies, we attempted to directly introduce  $\text{Ag}(\text{i})$  salt into the reaction mixture for these clusters, but this approach resulted in the formation of crystals of  $\text{Ti}_2\text{Ag}_2$  (Fig. 2A).  $\text{Ti}_2\text{Ag}_2$  is a typical bimetallic cluster, with two  $\text{Ag}^{1+}$  and two  $\text{Ti}^{4+}$  ions arranged in a quadrilateral configuration, sandwiched between two oxidized-TC4A ligands (Fig. 2B). Each  $\text{Ag}^{1+}$  site maintains a coordination number of six, with the  $\text{Ag}^{1+}$  seamlessly integrated into the cluster core, effectively shielded from external exposure (Fig. 2C). The composition of  $\text{Ti}_2\text{Ag}_2$  was determined using electrospray ionization mass spectrometry (ESI-MS) (Fig. S28†), which revealed a +1 signal at  $m/z = 1794.18$ , corresponding to the species  $[\text{HTi}_2\text{Ag}_2\text{O}(\text{O-TC4A})_2]^+$ .

Interestingly, using  $\text{Ti}_{12}\text{L}_6$  crystals in reactions with  $\text{Ag}(\text{i})$  salts yielded distinctly different outcomes. Introducing  $\text{Ag}_2\text{SO}_4$  into DMF solution along with  $\text{Ti}_{12}\text{L}_6$  crystals and allowing the mixture to react at  $80$  °C for three days resulted in the formation of the known clusters  $\text{Ti}_2\text{Ag}_2\text{-DMF}$  and  $\text{Ti}_2\text{Ag}_4$ .<sup>34</sup> Subsequently, by switching the solvent to  $\text{CH}_3\text{CN}$ , rhombic  $\text{Ti}_{12}\text{Ag}_{4.5}$  crystals were obtained, emphasizing the critical role of solvent selection in steering the chemical pathway.  $\text{Ti}_2\text{Ag}_2\text{-DMF}$  and  $\text{Ti}_2\text{Ag}_4$  have typical bimetallic configurations, with two or four  $\text{Ag}^{1+}$  ions embedded between two  $\{\text{Ti}(\text{TC4A})\}$  units. In contrast, in  $\text{Ti}_{12}\text{Ag}_{4.5}$ , multiple  $\text{Ag}^{1+}$  ions are effectively anchored onto the surface of the  $\text{Ti}_{12}$  core without altering its intrinsic structure. SCXRD analysis revealed the structure of  $\text{Ti}_{12}\text{Ag}_{4.5}$  to be  $[\text{H}_{1.5}\text{-Ti}_{12}\text{Ag}_{4.5}\text{O}_{18}(\text{HTC4A})_6(\text{CH}_3\text{CN})_4]$ , with the cluster containing three crystallographically distinct sites for Ag. Structural



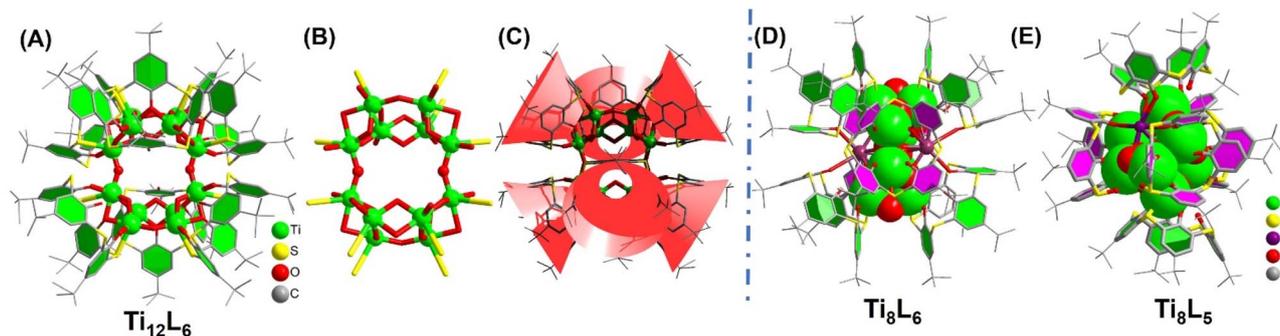


Fig. 1 (A) The overall structure of  $\text{Ti}_{12}\text{L}_6$ ; (B) the  $\text{Ti}_{12}\text{O}_{18}$  core in  $\text{Ti}_{12}\text{L}_6$ ; (C) the polyhedral arrangement of six calix moieties in  $\text{Ti}_{12}\text{L}_6$ ; (D) the overall structure of  $\text{Ti}_8\text{L}_6$ ; (E) the overall structure of  $\text{Ti}_8\text{L}_5$ .

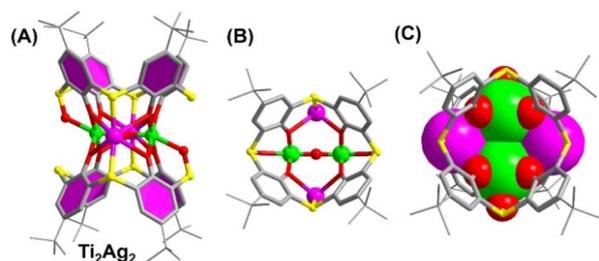


Fig. 2 (A) The overall structure of  $\text{Ti}_2\text{Ag}_2$ ; (B) coordination mode of oxidized TC4A in  $\text{Ti}_2\text{Ag}_2$ . (C) Comparison of the positions of the Ag and Ti sites in  $\text{Ti}_2\text{Ag}_2$ .

analysis demonstrated that the Ti-oxo core of  $\text{Ti}_{12}\text{Ag}_{4.5}$  closely mirrors the macrocyclic structure of  $\text{Ti}_{12}\text{L}_6$ , albeit with minor deviations (Fig. 3A). The  $\text{Ag}^{1+}$  sites are symmetrically divided and positioned on both the upper and lower facets of the Ti-oxo macrocycle (Fig. 4B). Ag1 and Ag2, coordinated through phenoxide, sulfur, and  $\mu\text{-O}_2^{2-}$ , are placed between two TC4A ligands, exhibiting coordination numbers of 3 and 4, respectively. The distances between Ag1/Ag2 and the Ti-oxo core range from 2.392 to 2.607 Å. Notably, the Ag3 site, with an  $\text{O}_3\text{N}_2$  coordination environment, is defined by two phenoxide groups, one  $\mu\text{-O}_2^-$ , and two  $\text{CH}_3\text{CN}$ , with Ag-O bond lengths ranging from 2.649 to 2.774 Å and Ag-N distances of 2.056 and 2.215 Å. The

spatial arrangement of the Ag sites, especially the Ag3 sites proximal to the cluster surface as depicted in Fig. 3C, highlights their potential as catalytically active sites. This is particularly significant given the labile nature of the  $\text{CH}_3\text{CN}$  ligand, which may facilitate dynamic catalytic processes. Sites Ag1 and Ag2 exhibit full occupancy, while Ag3 displays a partial occupancy of 0.25. As a result, the average number of Ag sites in the cluster is 4.5, which is confirmed by the mass spectrometry analysis of  $\text{Ti}_{12}\text{Ag}_{4.5}$ . Matrix-assisted laser desorption/ionization time-of-flight mass spectrometry (MALDI-TOF-MS) analysis reveals six distinct peaks with a mass difference of 107.86, corresponding to the ion  $\{\text{H}_x\text{Ti}_{12}\text{Ag}_y\text{O}_{16}(\text{TC}_4\text{A})_6(\text{CH}_2\text{Cl}_2)\}^+$  (Fig. 3D) ( $x = 1-6$ ). This pattern suggests that the cluster contains six Ag sites, which can sequentially detach under ionization conditions. Additionally, the atomic ratio of Ag to Ti in the cluster, as determined by ICP analysis, is 2.63, which is in excellent agreement with the theoretical value of 2.66 (Table S2†).

From the above results, it is evident that the solvent choice significantly influences the reaction pathway of  $\text{Ti}_{12}\text{L}_6$  with Ag(I) salts;  $\text{CH}_3\text{CN}$  primarily leads to  $\text{Ti}_{12}\text{Ag}_{4.5}$ , whereas solvents like DMF result in different structures of  $\text{Ti}_2\text{Ag}_2\text{-DMF}$  and  $\text{Ti}_2\text{Ag}_4$ . The significant impact of seemingly minor variations in solvent choice on the synthesis outcomes is fascinating. To elucidate the formation mechanism of  $\text{Ti}_{12}\text{Ag}_{4.5}$ , its evolutionary process was monitored using ESI-MS.<sup>39</sup> Time-resolved ESI-MS analysis of the reaction mixture, containing  $\text{Ti}_{12}\text{L}_6$  crystals and  $\text{Ag}_2\text{SO}_4$  in

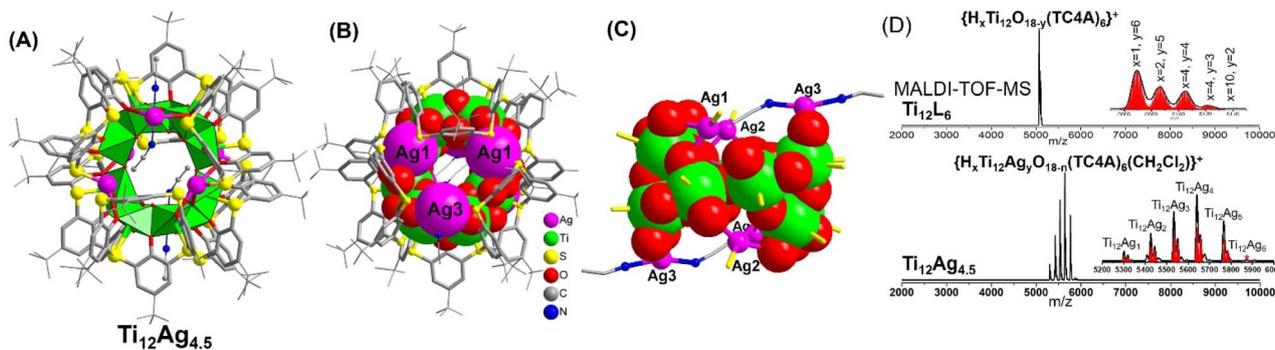


Fig. 3 (A) The overall structure of  $\text{Ti}_{12}\text{Ag}_{4.5}$ ; (B) space-filling model of the structure of  $\text{Ti}_{12}\text{Ag}_{4.5}$ , highlighting the exposed Ag atoms on the surface; (C) bonding mode of six  $\text{Ag}^{1+}$  sites to the titanium oxide core; (D) positive-mode MALDI-TOF-MS of  $\text{Ti}_{12}\text{L}_6$  and  $\text{Ti}_{12}\text{Ag}_{4.5}$  in  $\text{CH}_2\text{Cl}_2$  solution.



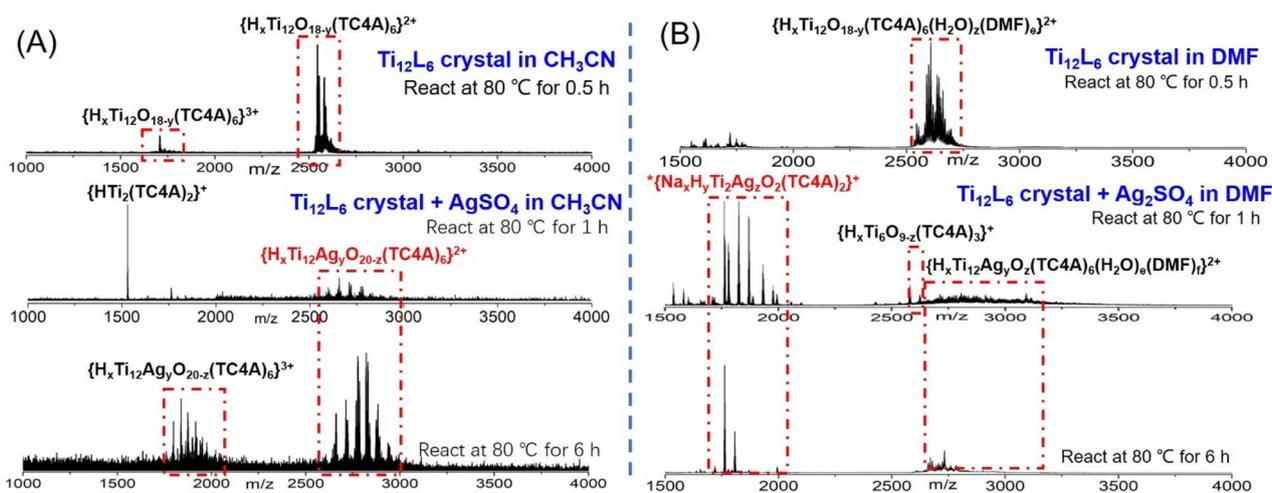


Fig. 4 Time-dependent ESI-MS for the reaction of the  $\text{Ti}_{12}\text{L}_6$  crystals and  $\text{Ag}_2\text{SO}_4$  in  $\text{CH}_3\text{CN}$  (A) or DMF (B) solution at  $80^\circ\text{C}$  at 0 h, 1 h and 6 h.

$\text{CH}_3\text{CN}$ , captured data at various intervals (Fig. 4A). Initially, ESI-MS detected two principal signal sets corresponding to the +2 and +3 charge states of  $\{\text{H}_x\text{Ti}_{12}\text{O}_{18-y}(\text{TC4A})_6\}$ , indicating that  $\text{Ti}_{12}\text{L}_6$  maintained its integrity in the early stages of the reaction. After heating at  $80^\circ\text{C}$  for one hour, new signals emerged, with a strong peak corresponding to  $\{\text{HTi}_2(\text{TC4A})_2\}^+$ , resulting from the fragmentation of  $\text{Ti}_{12}\text{L}_6$ . Additionally, subtle signals in the  $m/z$  range of 2000–2500, likely representing  $\{\text{Ti}_{12}\text{Ag}_x\text{O}_{20-z}(\text{TC4A})_6\}^{2+}$ , were observed. By the six-hour mark, the spectrum displayed distinct signal sets aligned with the +2 and +3 charge states of the  $\{\text{H}_x\text{Ti}_{12}\text{Ag}_x\text{O}_{20-z}(\text{TC4A})_6\}$  species, indicating a complete transformation of  $\text{Ti}_{12}\text{L}_6$  into  $\text{Ti}_{12}\text{Ag}_{4.5}$ .

Conversely, in a DMF environment, ESI-MS revealed a completely different reaction scenario (Fig. 4B). Initially,  $\text{Ti}_{12}\text{L}_6$  also maintained its structure in DMF (Fig. S34<sup>†</sup>). One hour post  $\text{Ag}(1)$  salt introduction, ESI-MS revealed the breakdown of the macrocycle, detecting  $\{\text{H}_x\text{Ti}_6\text{O}_z(\text{TC4A})_3\}^+$  and  $\{\text{H}_x\text{Ti}_2\text{O}_z(\text{TC4A})_2\}^+$  species. Notably, the emergence of  $\{\text{H}_x\text{Ti}_2\text{Ag}_y\text{O}_z(\text{TC4A})_2\}^+$  ( $x = 2-4$ ) clarified the formation of  $\text{Ti}_2\text{Ag}_4$  and  $\text{Ti}_2\text{Ag}_2$ -DMF clusters. By the six-hour mark, these signals intensified significantly, highlighting the progressive formation of these clusters in the DMF solution.

These findings indicate that the synthesis of  $\text{Ti}_{12}\text{Ag}_{4.5}$  is not merely a simple process of  $\text{Ag}^{1+}$  adsorption onto the  $\text{Ti}_{12}\text{L}_6$  carrier. Instead, it involves a complex sequence of fragmentation and subsequent reassembly (Fig. 5). Under solvothermal conditions, the  $\text{Ti}_{12}\text{L}_6$  framework undergoes a fragmentation process, resulting in the formation of  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  units. A dynamic equilibrium forms between the larger  $\{\text{Ti}_{12}\text{O}_{12}(\text{TC4A})_6\}$  structure and these smaller  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  units. In the presence of  $\text{CH}_3\text{CN}$  solvent, during the reassembly phase, these  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  fragments coordinate with  $\text{Ag}^{1+}$  ions, facilitating the formation of  $\text{Ti}_{12}\text{Ag}_{4.5}$ . Conversely, using DMF as the solvent leads to a transformation of the  $\{\text{Ti}_2\text{O}(\text{TC4A})\}$  units into more complex  $\{\text{Ti}_2\text{O}(\text{TC4A})_2\}$  structures. These structures then complex with  $\text{Ag}^{1+}$  ions to form  $\text{Ti}_2\text{Ag}_2$ -DMF and  $\text{Ti}_2\text{Ag}_4$ , highlighting a distinct synthetic pathway that is significantly influenced by the choice of solvent.

### Electrochemical $\text{CO}_2$ reduction

$\text{Ag}$ -based nanoclusters are optimal catalysts for electrocatalytic  $\text{CO}_2$  reduction reactions.<sup>40–42</sup> Tuning the coordination environment of  $\text{Ag}$  sites within the clusters is a key strategy to boost their catalytic activity and tune the selectivity for  $\text{CO}$  production.<sup>43–51</sup> From the structural comparison provided, it is clear that the distribution of  $\text{Ag}$  sites in the two  $\text{Ti}$ - $\text{Ag}$  clusters,  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$ , is significantly different. For bimetallic  $\text{Ti}_2\text{Ag}_2$ ,  $\text{Ag}^{1+}$  and  $\text{Ti}^{4+}$  sites are indistinguishably mixed within the core of the cluster. In contrast,  $\text{Ti}^{4+}$  sites of  $\text{Ti}_{12}\text{Ag}_{4.5}$  are embedded in the  $\text{Ti}$ -oxo core, while  $\text{Ag}^{1+}$  sites are strategically distributed across the cluster surface. These structural differences between  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$  provide a unique platform for investigating how variations in the  $\text{Ag}$  environments affect their catalytic activity.<sup>52,53</sup>

Powder X-ray diffraction (PXRD) analysis shows that the  $\text{Ti}_{12}\text{Ag}_{4.5}$  crystal maintains its crystalline structure even after exposure to a highly alkaline 1 M  $\text{KOH}$  solution for 24 hours (Fig. S35<sup>†</sup>). Given the resilience of  $\text{Ti}_{12}\text{Ag}_{4.5}$ , its  $\text{eCO}_2\text{RR}$  activity was assessed in a three-compartment flow cell with 1 M  $\text{KOH}$  as the electrolyte. Linear sweep voltammetry (LSV) results

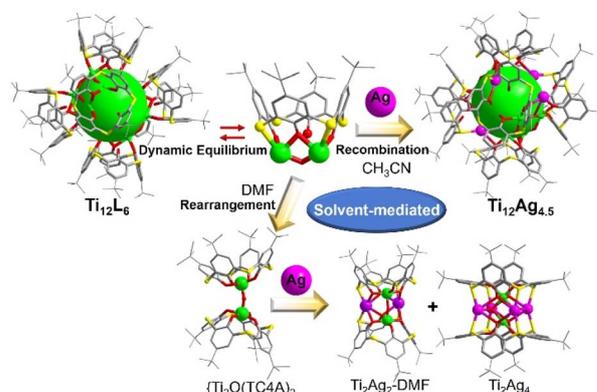


Fig. 5 Schematic diagram illustrating the solvent-mediated self-assembly process transitioning from  $\text{Ti}_{12}\text{L}_6$  to  $\text{Ti}_{12}\text{Ag}_{4.5}$ .



indicated a significantly higher current density and more positive onset potential for both the  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$  clusters in the  $\text{CO}_2$  flow electrolyzer compared to the  $\text{N}_2$ -purged system, confirming their  $\text{CO}_2$  reduction capability, as illustrated in Fig. 6A. Gas chromatography detected only  $\text{CO}$  and  $\text{H}_2$  as products, with no other liquid products identified by  $^1\text{H}$  NMR spectroscopy (Fig. S39<sup>†</sup>). Control experiments under  $\text{N}_2$ -saturated conditions yielded no carbon-reduction products. Isotopic tracing experiments with  $^{13}\text{CO}_2$  through GC-MS confirmed the production of  $^{13}\text{CO}$  ( $m/z = 29$ ) (Fig. S40<sup>†</sup>). Additionally, the primary electrocatalytic product of the  $\text{Ti}_{12}\text{L}_6$  catalyst was identified as  $\text{H}_2$ , indicating that the  $\text{Ag}^{1+}$  components of these clusters predominantly drive the catalytic activity (Fig. S37<sup>†</sup>).

Fig. 6B and C illustrate the trends in product distribution across varying potentials for two distinct clusters. In a  $\text{CO}_2$ -saturated environment,  $\text{Ti}_{12}\text{Ag}_{4.5}$  consistently exhibits a high  $\text{FE}_{\text{CO}}$  production, maintaining over 82.0% across an extensive potential range from  $-0.4$  V to  $-1.8$  V vs. RHE, peaking at 92.7% at a higher potential of  $-1.4$  V (Table S3<sup>†</sup>). However, for  $\text{Ti}_2\text{Ag}_2$ , the predominant reaction between  $-0.6$  V and  $-1.0$  V is  $\text{CO}_2$  reduction, reaching its highest  $\text{FE}_{\text{CO}}$  of 85.1% at  $-0.8$  V. Beyond this, the reaction is largely overtaken by  $\text{H}_2$  evolution in the potential range from  $-1.2$  to  $-1.8$  V, leading to a progressive decline in  $\text{FE}_{\text{CO}}$  as potential increases. At  $-1.8$  V, the  $\text{FE}_{\text{CO}}$  of  $\text{Ti}_2\text{Ag}_2$  plummets to merely 21.2%, whereas  $\text{Ti}_{12}\text{Ag}_{4.5}$  still manages to maintain an  $\text{FE}_{\text{CO}}$  of 83.25%. Additionally, the  $\text{CO}$  partial current density ( $J_{\text{CO}}$ ) for both clusters was also analyzed (Fig. 6D). The  $J_{\text{CO}}$  for  $\text{Ti}_{12}\text{Ag}_{4.5}$  reached an impressive  $130.1 \text{ mA cm}^{-2}$  at  $-1.8$  V, which is above 2.4 times greater than that of  $\text{Ti}_2\text{Ag}_2$ . This comparative analysis emphasizes the pronounced differences in catalytic efficiencies between two clusters, attributing  $\text{Ti}_{12}\text{Ag}_{4.5}$ 's superior performance to its unique structural configuration and effective  $\text{Ag}^{1+}$  site utilization.

Electrocatalytic stability is a key indicator for evaluating the performance of electrocatalysts in the  $\text{eCO}_2\text{RR}$ . We employed PXRD to analyze the reduction of  $\text{Ag}^+$  in  $\text{Ti}_{12}\text{Ag}_{4.5}$  after reaction

at different applied voltages (Fig. S44<sup>†</sup>). PXRD analysis reveals that the catalyst remains stable when the applied voltage is below  $-1.8$  V. However, when the voltage exceeds  $-1.8$  V, signals corresponding to  $\text{Ag}$  nanoparticles appear, indicating the reduction of  $\text{Ag}^+$  to metallic  $\text{Ag}$ . To further evaluate the durability of the catalyst, we conducted a rigorous 11-hour chronoamperometric test at  $-1.4$  V. During this process, the current density remained above  $100 \text{ mA cm}^{-2}$ , and the FE for  $\text{CO}$  remained stable above 85.0% (Fig. 6E). Additionally, ESI-MS analysis of the catalysts after electrolysis showed a signal for the  $\{\text{H}_x\text{Ti}_{12}\text{Ag}_6\text{O}_{18-2z}(\text{TC4A})_6\}^{2+}$  species, confirming that the structural integrity of the  $\text{Ti}_{12}\text{Ag}_{4.5}$  catalyst was maintained (Fig. S45<sup>†</sup>). Further characterization by transmission electron microscopy, X-ray photoelectron spectroscopy, and infrared spectroscopy showed that the catalyst maintained its chemical composition and structural stability during the electrolysis process (Fig. S47–S49<sup>†</sup>). Differential pulse voltammetry (DPV) measurements reveal that the electrochemical gap of  $\text{Ti}_{12}\text{Ag}_{4.5}$  is 1.91 V (Fig. S50<sup>†</sup>), which is greater than the 1.32 V observed for  $\text{Ti}_2\text{Ag}_2$ . This larger electrochemical gap further suggests enhanced stability of  $\text{Ti}_{12}\text{Ag}_{4.5}$  during the electrocatalytic process. The stability of  $\text{Ag}^+$  in the  $\text{Ti}_{12}\text{Ag}_{4.5}$  clusters can be attributed to the strong electronic and structural stabilization provided by the Ti-oxo support. This unique characteristic not only preserves the active sites but also prevents the competitive reduction of  $\text{Ag}^+$ , thereby enhancing the suitability of these clusters for  $\text{CO}_2$  reduction.

The hypothesized mechanism for  $\text{CO}_2$  reduction to  $\text{CO}$  using Ag-based catalysts follows the pathway:  $\text{CO}_2(\text{g}) \rightarrow * \text{COOH} \rightarrow * \text{CO} \rightarrow \text{CO}(\text{g})$ .<sup>54–57</sup> To validate this mechanism, we utilized *in situ* electrochemical attenuated total reflection surface-enhanced infrared absorption spectroscopy (ATR-SEIRAS). This technique allows for real-time monitoring of the absorption of evanescent waves by substances on the catalyst surface, providing direct insight into the reaction dynamics. We set the potential range from  $-0.5$  V to  $-1.3$  V and monitored changes in absorption peaks with  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$  as the electrocatalysts (Fig. 6F). The spectra display similarities, including

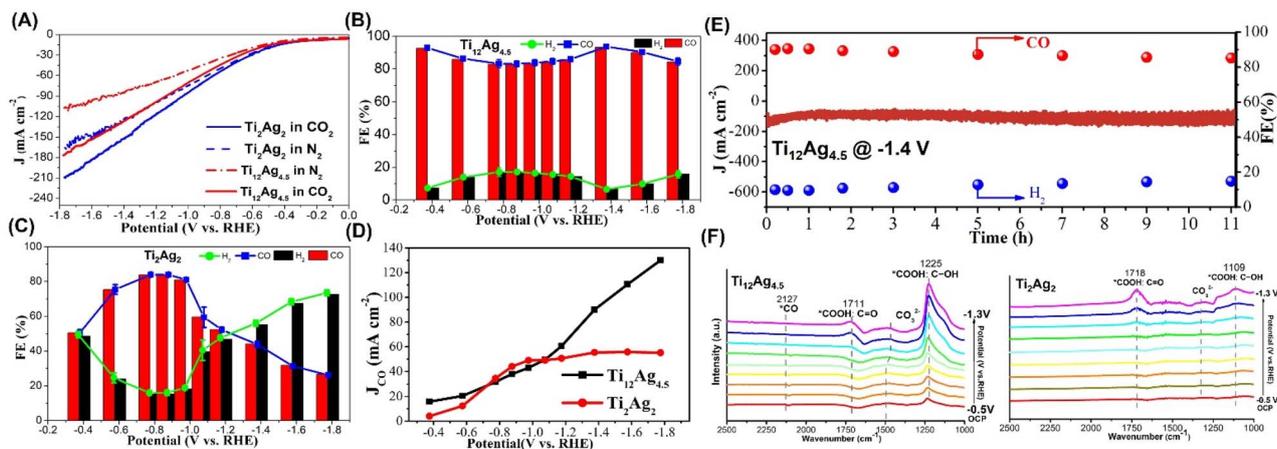


Fig. 6 (A) LSV of samples in  $\text{N}_2$  or  $\text{CO}_2$  saturated 1 M KOH solution; (B) FE values of  $\text{Ti}_{12}\text{Ag}_{4.5}$  at different voltages; (C) FE values of  $\text{Ti}_2\text{Ag}_2$  at different voltages; (D)  $\text{CO}$  partial current density ( $j_{\text{CO}}$ ); (E)  $I-t$  test and  $\text{FE}_{\text{CO}}$  values of  $\text{Ti}_{12}\text{Ag}_{4.5}$  at  $-1.4$  V vs. RHE in different time periods; (F) the ATR-SEIRAS results from  $2500$  to  $1000 \text{ cm}^{-1}$  of  $\text{Ti}_2\text{Ag}_2$  and  $\text{Ti}_{12}\text{Ag}_{4.5}$ .



a pronounced peak at  $1225\text{ cm}^{-1}$ , attributed to C–OH stretching in  $^*\text{COOH}$ , which intensifies with increasing voltage. Another peak at  $1711\text{ cm}^{-1}$ , corresponding to C=O stretching in  $^*\text{COOH}$ , also increases in intensity from  $-0.5\text{ V}$  to  $-1.3\text{ V}$ , suggesting a rise in the surface coverage of  $^*\text{COOH}$  species with increasing voltage.<sup>58,59</sup> Additionally, a weak signal at  $2127\text{ cm}^{-1}$ , attributed to the Ag– $^*\text{CO}$  vibration mode, indicates the presence of  $^*\text{CO}$  adsorbed on the catalyst surface, especially at lower potentials where the  $^*\text{CO}$  band intensity shows a slight increase. Notably, the intermediate characteristic peak of  $\text{Ti}_2\text{Ag}_2$  becomes distinctly observable only from an electrode potential of approximately  $-1.1\text{ V}$ , while the characteristic peaks of  $\text{Ti}_{12}\text{Ag}_{4.5}$  are already evident at  $-0.5\text{ V}$ . This observation indicates that  $\text{Ti}_{12}\text{Ag}_{4.5}$  demonstrates a higher reaction activity and stronger catalytic proficiency for the eCO<sub>2</sub>RR, aligning with experimental findings.

Density Functional Theory (DFT) calculations were conducted to elucidate the reactivity of two specifically designed clusters,  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$ . These models were optimized to mirror their actual crystal structures, simplified by replacing the *tert*-butyl groups on the TC4A with H for faster computational convergence. The results of these optimizations are depicted in the Gibbs free energy diagrams for both the eCO<sub>2</sub>RR and the HER, as presented in Fig. 7A. DFT calculations specifically focused on the energetics of each step, revealing that the formation of the  $^*\text{COOH}$  intermediate is the rate-determining step in the CO<sub>2</sub>RR process. A critical finding from our study is the calculated Gibbs free energy for the formation of  $^*\text{COOH}$  on the Ag<sub>3</sub> site in  $\text{Ti}_{12}\text{Ag}_{4.5}$ , which was notably low at  $0.55\text{ eV}$ . This value contrasts with the corresponding energy of  $0.88\text{ eV}$  for the same process within  $\text{Ti}_2\text{Ag}_2$ . This substantial difference highlights that the exposed Ag sites on  $\text{Ti}_{12}\text{Ag}_{4.5}$  are much more energetically favorable for catalyzing the conversion of CO<sub>2</sub> to CO compared to those on bimetallic  $\text{Ti}_2\text{Ag}_2$  (Fig. 7B). Additionally, the Gibbs free energies for hydrogen adsorption ( $^*\text{H}$ ) were calculated, showing high values of  $2.46\text{ eV}$  for both clusters, indicating that neither  $\text{Ti}_2\text{Ag}_2$  nor  $\text{Ti}_{12}\text{Ag}_{4.5}$  is favorable for the formation of H<sub>2</sub>. This finding is important as it underscores

the higher selectivity of both clusters for the CO<sub>2</sub>RR-to-CO pathway compared to the HER.

By comparing the Gibbs free energy diagrams of the eCO<sub>2</sub>RR and HER, the exceptional catalytic efficiency of  $\text{Ti}_{12}\text{Ag}_{4.5}$  is clearly linked to its unique Ag coordination. This coordination is supported by a titanium–oxo core, with Ag sites evenly distributed across the cluster surface. Specifically, the Ag active sites in  $\text{Ti}_{12}\text{Ag}_{4.5}$  exhibit a d-band center ( $\epsilon_d$ ) that is closer to the Fermi level at  $-3.04\text{ eV}$ . As a comparison, the bimetallic cluster  $\text{Ti}_2\text{Ag}_2$  exhibits a lower  $\epsilon_d$  value of  $-3.47\text{ eV}$ , likely attributed to the absence of the unique support effects found in  $\text{Ti}_{12}\text{Ag}_{4.5}$ . Furthermore, the projected density of states (PDOS) for  $\text{Ti}_{12}\text{Ag}_{4.5}$  shows higher and narrower peaks at energies near the Fermi level, suggesting a higher and more localized density of electronic states (Fig. S53†). This enhanced electronic configuration facilitates stronger interactions with adsorbate  $^*\text{COOH}$  molecules, improving the activation and subsequent transformation of CO<sub>2</sub>. These electronic characteristics are critical for reactions requiring complex electron interactions, thus positioning  $\text{Ti}_{12}\text{Ag}_{4.5}$  as a more effective catalyst for CO<sub>2</sub> reduction.

## Conclusions

In summary, this study has designed and synthesized a new type of crystalline oxide cluster-stabilized single-atom material that can more precisely emulate the structural and reactive characteristics of oxide-supported single-atom catalysts at the molecular level. We have discovered a solvent-mediated assembly process that transforms the calixarene-stabilized titanium oxide cluster,  $\text{Ti}_{12}\text{L}_6$ , into the oxide-supported cluster,  $\text{Ti}_{12}\text{Ag}_{4.5}$ . This transformed cluster prominently features six accessible single Ag<sup>1+</sup> sites on its surface. The distinctive structure of  $\text{Ti}_{12}\text{Ag}_{4.5}$  has demonstrated superior catalytic performance in the eCO<sub>2</sub>RR, outperforming the traditional bimetallic cluster  $\text{Ti}_2\text{Ag}_2$  in terms of reactivity and CO selectivity. *In situ* ATR-SEIRAS and DFT calculations were employed to investigate the catalytic mechanism, complemented by a structural comparison between  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$  to clarify the factors underlying their different performances. These insights emphasize the importance of controlling the distribution of active metal sites on the surface of the cluster. This study promotes the intentional design of interactions between active surface sites and their cluster support, potentially establishing a new paradigm in single-atom catalyst design by significantly enhancing catalytic activities.

## Data availability

The data that support the findings of this study are available in the main text and the ESL.†

## Author contributions

C. L. supervised the project and conceived the idea. R. X. M., L. C. Z and L. K. W carried out synthesis, characterization and catalytic experiments of clusters. Q. T. and L. P. L performed the calculations for this article. Y.-L. S. was responsible for the

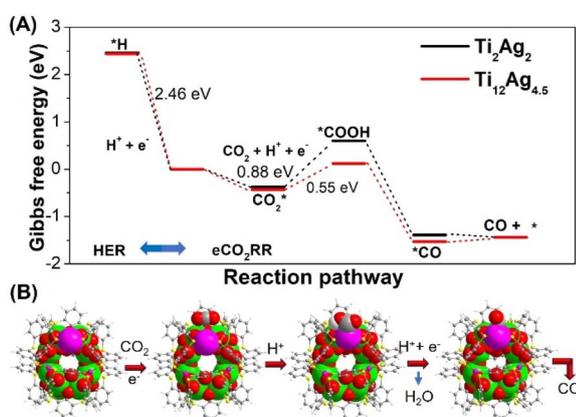


Fig. 7 (A) Free energy diagrams for the eCO<sub>2</sub>RR and HER on  $\text{Ti}_{12}\text{Ag}_{4.5}$  and  $\text{Ti}_2\text{Ag}_2$ ; (B) schematic diagram of the eCO<sub>2</sub>RR process on  $\text{Ti}_{12}\text{Ag}_{4.5}$ .



single crystal testing. C. L. wrote the manuscript. All authors discussed the experimental results.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

This work was supported by the Natural Science Foundation of Hunan Province (2023JJ30650), the Central South University Innovation-Driven Research Programme (2023CXQD061), and the National Natural Science Foundation of China (21901256 and 21805170). We thank Professor Mingzhao Chen and Dr Ning Wang from Guangzhou University for the mass spectrometry measurements.

## Notes and references

- L. Liu and A. Corma, *Chem. Rev.*, 2018, **118**, 4981–5079.
- Y. Guo, S. Mei, K. Yuan, D. J. Wang, H. C. Liu, C. H. Yan and Y. W. Zhang, *ACS Catal.*, 2018, **8**, 6203–6215.
- M. Murdoch, G. I. N. Waterhouse, M. A. Nadeem, J. B. Metson, M. A. Keane, R. F. Howe, J. Llorca and H. Idriss, *Nat. Chem.*, 2011, **3**, 489–492.
- A. vonWeber and S. L. Anderson, *Acc. Chem. Res.*, 2016, **49**, 2632–2639.
- B. Qiao, A. Wang, X. Yang, L. F. Allard, Z. Jiang, Y. Cui, J. Liu, J. Li and T. Zhang, *Nat. Chem.*, 2011, **3**, 634–641.
- S. Yang, J. Kim, Y. J. Tak, A. Soon and H. Lee, *Angew. Chem., Int. Ed.*, 2016, **55**, 2058–2062.
- J. Zhang, X. Wu, W. C. Cheong, W. Chen, R. Lin, J. Li, L. Zheng, W. Yan, L. Gu, C. Chen, Q. Peng, D. Wang and Y. D. Li, *Nat. Commun.*, 2018, **9**, 1002.
- C. M. Zhao, X. Y. Dai, T. Yao, W. X. Chen, X. Q. Wang, J. Wang, J. Yang, S. Q. Wei, Y. Wu and Y. D. Li, *J. Am. Chem. Soc.*, 2017, **139**, 8078–8081.
- J. D. Yi, X. P. Gao, H. Zhou, W. Chen and Y. Wu, *Angew. Chem., Int. Ed.*, 2022, e202212329.
- R. Lang, X. Du, Y. Huang, X. Jiang, Q. Zhang, Y. Guo, K. Liu, B. Qiao, A. Wang and T. Zhang, *Chem. Rev.*, 2020, **120**, 11986–12043.
- X. F. Yang, A. Wang, B. Qiao, J. Li, J. Liu and T. Zhang, *Acc. Chem. Res.*, 2013, **46**, 1740–1748.
- Z. Huang, X. Gu, Q. Cao, P. Hu, J. Hao, J. Li and X. Tang, *Angew. Chem., Int. Ed.*, 2012, **51**, 4198–4203.
- C. T. Campbell, *Acc. Chem. Res.*, 2013, **46**, 1712–1719.
- R. Jin, C. Zeng, M. Zhou and Y. Chen, *Chem. Rev.*, 2016, **116**, 10346–10413.
- P. Liu, Y. Zhao, R. Qin, L. Gu, P. Zhang, G. Fu and N. Zheng, *Sci. Bull.*, 2018, **63**, 675–682.
- W. H. Fang, L. Zhang and J. Zhang, *Chem. Soc. Rev.*, 2018, **47**, 404–421.
- P. Coppens, Y. Chen and E. Trzop, *Chem. Rev.*, 2014, **114**, 9645–9661.
- L. Rozes and C. Sanchez, *Chem. Soc. Rev.*, 2011, **40**, 1006–1030.
- Y. Lv, J. Cheng, A. Steiner, L. Gan and D. S. Wright, *Angew. Chem., Int. Ed.*, 2014, **53**, 1934–1938.
- C. Zhao, Y. Z. Han, S. Dai, X. Chen, J. Yan, W. Zhang, H. Su, S. Lin, Z. Tang, B. K. Teo and N. Zheng, *Angew. Chem., Int. Ed.*, 2017, **56**, 16252–16256.
- G. Zhang, C. Liu, D. L. Long, L. Cronin, C. H. Tung and Y. Wang, *J. Am. Chem. Soc.*, 2016, **138**, 11097–11100.
- W. H. Fang, L. Zhang and J. Zhang, *J. Am. Chem. Soc.*, 2016, **138**, 7480–7483.
- M. Y. Gao, F. Wang, Z. G. Gu, D. X. Zhang, L. Zhang and J. Zhang, *J. Am. Chem. Soc.*, 2016, **138**, 2556–2559.
- J. L. Hou, N. H. Huang, D. Acharya, Y. X. Liu, J. Y. Zhu, J. X. Teng, Z. Wang, K. Q. Qu, X. X. Zhang and D. Sun, *Chem. Sci.*, 2024, **15**, 2655–2664.
- M. Zhang, M. Lu, M.-Y. Yang, J.-P. Liao, Y.-F. Liu, H.-J. Yan, J.-N. Chang, T.-Y. Yu, S.-L. Li and L. Y. Qian, *eScience*, 2023, **3**, 100116.
- Y. J. Liu, P. Shao, M. Y. Gao, W. H. Fan and J. Zhang, *Inorg. Chem.*, 2020, **59**, 11442–11448.
- X. Fan, F. Yuan, D. Li, S. Chen, Z. Cheng, Z. Zhang, S. Xiang, S. Q. Zang, J. Zhang and L. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 12949–12954.
- M. Y. Gao, K. Wang, Y. Y. Sun, D. J. Li, B. Q. Song, Y. H. Andaloussi, M. J. Zaworotko, J. Zhang and L. Zhang, *J. Am. Chem. Soc.*, 2020, **142**, 12784–12790.
- N. Li, J.-M. Lin, R.-H. Li, J.-W. Shi, L.-Z. Dong, J. Liu, J. He and Y. Q. Lan, *J. Am. Chem. Soc.*, 2023, **145**, 16098–16108.
- E. M. Han, R. X. Meng, Y. Q. Tian, J. Yan, K. Y. Liu and C. Liu, *Chem. Commun.*, 2023, **59**, 11097–11100.
- S. Chen, Z. N. Chen, W. H. Fang, W. Zhuang, L. Zhang and J. Zhang, *Angew. Chem., Int. Ed.*, 2019, **58**, 10932–10935.
- D. T. Geng, X. Han, Y. F. Bi, Y. C. Qin, Q. Li, L. L. Huang, K. Zhou, L. J. Song and Z. P. Zheng, *Chem. Sci.*, 2018, **9**, 8535–8541.
- S. T. Wang, X. H. Gao, X. X. Hang, X. F. Zhu, H. T. Han, W. P. Liao and W. Chen, *J. Am. Chem. Soc.*, 2016, **138**, 16236–16239.
- Y. Q. Tian, W. L. Mu, L. L. Wu, X. Y. Yi, J. Yan and C. Liu, *Chem. Sci.*, 2023, **14**, 10212–10218.
- Z. Wang, L. Li, L. Feng, Z. Y. Gao, C. H. Tung, L. S. Zheng and D. Sun, *Angew. Chem., Int. Ed.*, 2022, **61**, e202200823.
- Z. Wang, H. F. Su, Y. W. Gong, Q. P. Qu, Y. F. Bi, C. H. Tung, D. Sun and L. S. Zheng, *Nat. Commun.*, 2020, **11**, 308.
- Z. Wang, F. Alkan, C. M. Aikens, M. Kurmoo, Z. Y. Zhang, K. P. Song, C. H. Tung and D. Sun, *Angew. Chem., Int. Ed.*, 2022, **61**, e202206742.
- Z. J. Guan, F. Hu, S. F. Yuan, Z. A. Nan, Y. M. Lin and Q. M. Wang, *Chem. Sci.*, 2019, **10**, 3360–3365.
- X.-M. Luo, S. Huang, P. Luo, K. Ma, Z.-Y. Wang, X.-Y. Dong and S.-Q. Zang, *Chem. Sci.*, 2022, **13**, 11110–11118.
- L. J. Li, Y. T. Luo, Y. Q. Tian, P. Wang, X. Y. Yi, J. Yan, Y. Pei and C. Liu, *Inorg. Chem.*, 2023, **62**, 14377–14384.
- Z. Liu, J. Chen, B. Li, D.-e. Jiang, L. Wang, Q. Yao and J. Xie, *J. Am. Chem. Soc.*, 2024, **146**(17), 11773–11781.
- S. L. Zhuang, D. Chen, L. W. Liao, Y. Zhao, N. Xia, W. Zhang, C. Wang, J. Yang and Z. Wu, *Angew. Chem., Int. Ed.*, 2020, **59**, 3073–3077.



- 43 J. Y. Xu, L. Xiong, X. Cai, S. S. Tang, A. C. Tang, X. Liu, Y. Pei and Y. Zhu, *Chem. Sci.*, 2022, **13**, 2778–2782.
- 44 X. Liu, E. D. Wang, M. Zhou, Y. Wan, Y. K. Zhang, H. Q. Liu, Y. Zhao, J. Li, Y. Gao and Y. Zhu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202207685.
- 45 S. Li, A. V. Nagarajan, D. R. Alfonso, M. K. Sun, D. R. Kauffman, G. Mpourmpakis and R. Jin, *Angew. Chem., Int. Ed.*, 2021, **60**, 6351–6356.
- 46 S. Zhao, N. Austin, M. Li, Y. Song, S. D. House, S. Bernhard, J. C. Yang, G. Mpourmpakis and R. Jin, *ACS Catal.*, 2018, **8**, 4996–5001.
- 47 L. Tang, Y. Luo, X. Ma, B. Wang, M. Ding, R. Wang, P. Wang, Y. Pei and S. Wang, *Angew. Chem., Int. Ed.*, 2023, e202300553.
- 48 L. J. Li, W. L. Mu, Y. Q. Tian, W. D. Yu, L. Y. Li, J. Yan and C. Liu, *Chem. Sci.*, 2024, **15**, 7643–7650.
- 49 G. C. Deng, H. Yun, M. S. Bootharaju, F. Sun, K. Lee, X. L. Liu, S. Yoo, Q. Tang, Y. J. Hwang and T. Hyeon, *J. Am. Chem. Soc.*, 2023, **145**(50), 27407–27414.
- 50 L. B. Qin, F. Sun, X. S. Ma, G. Y. Ma, Y. Tang, L. Wang, Q. Tang, R. Jin, Z. Tang and Z. H. Tang, *Angew. Chem., Int. Ed.*, 2021, **60**, 26136–26141.
- 51 X. S. Ma, F. Sun, L. B. Qin, Y. G. Liu, X. W. Kang, L. K. Wang, D. E. Jiang, Q. Tang and Z. H. Tang, *Chem. Sci.*, 2022, **13**, 10149–10158.
- 52 S. Yoo, S. Yoo, G. C. Deng, F. Sun, K. Lee, H. Jang, C. W. Lee, X. L. Liu, J. Jang, Q. Tang, Y. J. Hwang, T. Hyeon and M. S. Bootharaju, *Adv. Mater.*, 2024, **36**, 2313032.
- 53 X. L. Liu, T. Ki, G. C. Deng, S. Yoo, K. Lee, B.-H. Lee, T. Hyeon and M. S. Bootharaju, *Nanoscale*, 2024, **16**, 12329–12344.
- 54 G. Deng, J. Kim, M. S. Bootharaju, F. Sun, K. Lee, Q. Tang, Y. J. Hwang and T. Hyeon, *J. Am. Chem. Soc.*, 2023, **145**, 3401–3407.
- 55 J. Wang, F. Xu, Z. Y. Wang, S. Q. Zang and T. C. W. Mak, *Angew. Chem., Int. Ed.*, 2022, **61**, e202207492.
- 56 L. J. Liu, Z. Y. Wang, Z. Y. Wang, R. Wang, S. Q. Zang and T. C. Mak, *Angew. Chem., Int. Ed.*, 2022, **61**, e202205626.
- 57 Y. F. Lu, L. Z. Dong, J. Liu, R. X. Yang, J. J. Liu, Y. Zhang, L. Zhang, Y. R. Wang, S. L. Li and Y. Q. Lan, *Angew. Chem., Int. Ed.*, 2021, **60**, 26210–26217.
- 58 D. Wang, J. J. Mao, C. C. Zhang, J. W. Zhang, J. S. Li, Y. Zhang and Y. F. Zhu, *eScience*, 2023, **3**, 100119.
- 59 X. Wang, M. H. Yu and X. L. Feng, *eScience*, 2023, **3**, 100141.

