



Cite this: *Chem. Sci.*, 2025, 16, 13241

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Amine groups alter product selectivity and rate of catalytic hydride transfer reactions†

Santanu Pattanayak,‡ Rachel E. Siegel,‡ Yiming Liu, James C. Fettinger  and Louise A. Berben \*

Primary amines are common functional groups in the reaction environment surrounding an (electro) catalyst, and this includes catalysts ranging from metalloenzymes surrounded by amino acids, to electrocatalysts operating in amine industrial sorbents for CO<sub>2</sub> capture and conversion. This report explores the behavior of amine functional groups at the surface of an electrocatalyst. The possible effects of those amine secondary coordination sphere (SCS) groups on a CO<sub>2</sub> electro-reduction mechanism include stabilization of intermediates and positioning substrate near the active site. Two different clusters were synthesized: [PPN][Fe<sub>4</sub>N(CO)<sub>11</sub>(Ph<sub>2</sub>PCH<sub>2</sub>CH<sub>2</sub>NH<sub>2</sub>)] (PPN-1) has one amine, and [PPN][Fe<sub>4</sub>N(CO)<sub>10</sub>(Ph<sub>2</sub>PCH<sub>2</sub>CH<sub>2</sub>NH<sub>2</sub>)<sub>2</sub>] (PPN-2) has two covalently appended amine functional groups (PPN: bis(triphenylphosphine)iminium). Infra-red spectroscopic studies show a direct reaction of each cluster with CO<sub>2</sub> to afford an SCS carbamate functional group, and cyclic voltammetry investigations reveal a variety of roles for the amine SCS groups in the mechanism of catalyst hydride formation and hydride transfer (HT) to CO<sub>2</sub>. The most prominent effect of the amine functional group is stabilization of the intermediate hydride to lower formate yield. With PPN-1, these combined effects serve to shut down HT to CO<sub>2</sub>. With PPN-2, the combined effects result in some loss of selectivity, so that formate and H<sub>2</sub> mixtures (6 : 1) are obtained.

Received 30th October 2024  
Accepted 31st January 2025

DOI: 10.1039/d4sc07359b

rsc.li/chemical-science

## Introduction

Specific interactions of functional groups near the surface of heterogeneous electrocatalysts or near the active site of a molecular or biological catalyst,<sup>1,2</sup> are often responsible for the observed catalysis outcomes such as reaction rate, product selectivity, and overpotential, amongst others.<sup>3,4</sup> As specific examples in biology, carbonic anhydrase and hydrogenase activity have well-documented mechanisms. Carbonic anhydrase is an enzyme that catalyzes the reversible conversion of CO<sub>2</sub> and water into bicarbonate and protons.<sup>5</sup> In the active site of carbonic anhydrase, hydrogen bond (H-bond) donors are known to modulate p*K*<sub>a</sub> so that reversible proton transfer (PT) to CO<sub>2</sub> is possible at fast rates.<sup>6</sup> The [FeFe]-hydrogenase enzyme reduces H<sup>+</sup> into H<sub>2</sub> via a hydride transfer (HT) mechanism. In that mechanism, it has been proposed that amine functional groups in amino acids are involved both in the maturation process as well as catalysis, and that the role of amines is likely as a Lewis base.<sup>7</sup> It has also been proposed that amines are structurally important to [FeFe]-hydrogenases, where H-

bonding between the hydride of H<sub>hyd</sub> and the ADT-NH is thought to stabilize the structure.<sup>8</sup>

In biology, amine functional groups can have several roles, including as H-bond donors, or as Lewis basic sites that aid in proton transport. Similar roles are known in non-biological catalytic systems. It would be very useful to learn more about the multitude of roles that secondary coordination sphere (SCS) primary amine functional groups can play in the atomic level details of catalytic CO<sub>2</sub> reduction mechanisms. Specific examples of amine functional groups in electrocatalysis include a study on the role of amines at the surface of Ag and Cu electrocatalyst which promote CO<sub>2</sub> reduction. In that instance, multiple roles including H-bond stabilization of CO<sub>2</sub> and tuning the reorganization energy of the surrounding water were proposed.<sup>9–11</sup> Studies with molecular catalysts which probe the role of amine functional groups on CO<sub>2</sub> reduction catalysis include work where amines stabilize intermediate Fe–CO interactions so that further reduction to CH<sub>4</sub> can occur using an iron porphyrin complex,<sup>12</sup> and alternatively where amines stabilize a Co-carboxylate intermediate along a pathway to enhanced CO formation rate.<sup>13</sup> Amine functional groups have also been used as a proton shuttle to favor formate over CO production, from CO<sub>2</sub> reduction.<sup>14,15</sup>

Molecular models can provide mechanistic insights into possible roles that primary amine functional groups can have in CO<sub>2</sub> reduction catalysis. In this report, we focused on

Department of Chemistry, University of California, Davis, CA 95616, USA. E-mail: laberben@ucdavis.edu

† Electronic supplementary information (ESI) available: Experimental methods, electrochemical data, calculations and analysis of electrochemical data. See DOI: <https://doi.org/10.1039/d4sc07359b>

‡ These authors contributed equally.



installation of a primary amine SCS group at the surface of a small cluster electrocatalyst,  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  (Chart 1).<sup>16</sup> This electrocatalyst was chosen because we have previously demonstrated selective formation of formate using  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ : and that reaction mechanism involves a key hydride intermediate  $[\text{H-Fe}_4\text{N}(\text{CO})_{12}]^-$ , that selectively transfers  $\text{H}^-$  to  $\text{CO}_2$  to afford formate. In the work reported herein, multiple roles for the surface amine functional groups have been uncovered, including direct reaction with  $\text{CO}_2$  to afford carbamate anion and as a Lewis basic site to accept protons and yield ammonium which then serves as proton sources for hydride formation or as H-bond stabilization of the catalytic intermediate hydride  $[\text{HFe}_4\text{N}(\text{CO})_{12}]^-$ . The sometimes cooperative and sometimes competing effects of these various roles for surface amine groups on  $[\text{Fe}_4\text{N}(\text{CO})_{11}(\text{PPh}_2(\text{CH}_2)_2\text{NH}_2)]^-$  ( $1^-$ ) and  $[\text{Fe}_4\text{N}(\text{CO})_{10}(\text{PPh}_2(\text{CH}_2)_2\text{NH}_2)_2]^{2-}$  ( $2^-$ ) are discussed below. Optimization of the catalytic reaction conditions ultimately employs the amine groups on  $2^-$  for  $\text{CO}_2$  capture, and the observed rate constant for formate production is  $7.3 \text{ s}^{-1}$ . This rate constant is of the same order of magnitude reported for  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  to make formate,<sup>17</sup> and that result suggests that dissolved  $\text{CO}_2$  is the source of substrate.

## Results and discussion

### Synthesis of amine-substituted catalysts, $1^-$ and $2^-$

The SCS amine tagged phosphine substituted cluster  $\text{Et}_4\text{N}[\text{Fe}_4\text{N}(\text{CO})_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{NH}_2)]$  ( $\text{Et}_4\text{N-1}$ ) was synthesized in quantitative yield by addition of one equivalent of  $\text{Ph}_2\text{P}(\text{CH}_2)_2\text{NH}_2$  to  $[\text{Na}(\text{diglyme})_2][\text{Fe}_4\text{N}(\text{CO})_{12}]$ , followed by heating in THF at  $60^\circ\text{C}$  for 12 h, before  $\text{Et}_4\text{NCl}$  was used in a salt metathesis reaction that afforded  $\text{Et}_4\text{N-1}$ . The detailed synthetic procedures are given in the ESI†, and  $(\text{Et}_4\text{N})^+$  is the cation tetraethylammonium. Synthesis of doubly substituted  $\text{Et}_4\text{N}[\text{Fe}_4\text{N}(\text{CO})_{10}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{NH}_2)_2]$  ( $\text{Et}_4\text{N-2}$ ) was achieved in 65% yield; 3.5 equivalents of  $\text{Ph}_2\text{P}(\text{CH}_2)_2\text{NH}_2$  was heated at reflux with  $[\text{Na}(\text{diglyme})_2][\text{Fe}_4\text{N}(\text{CO})_{12}]$  in THF/toluene (1 : 3 v/v) for 24 h, followed by salt metathesis reaction with  $\text{Et}_4\text{NCl}$  and workup. Following identical salt metathesis procedures with  $\text{PPNCl}$ , we were also able to isolate  $\text{PPN-1}$  and  $\text{PPN-2}$  ( $\text{PPN}$  is the non-coordinating cation bis(triphenylphosphine)iminium). Throughout the manuscript, we henceforth refer to  $\text{Et}_4\text{N-1}$  or  $\text{PPN-1}$  and  $\text{Et}_4\text{N-2}$  or  $\text{PPN-2}$  as  $1^-$  and  $2^-$ , respectively.

Each of the clusters,  $1^-$  and  $2^-$ , was characterized by  $^1\text{H}$ ,  $^{13}\text{C}$ , and  $^{31}\text{P}$  NMR, and IR spectroscopy (Fig. S1–S7†); and the  $^{31}\text{P}$  NMR spectra each show a single sharp resonance approximately 70 ppm downfield from the free phosphine ligand ( $\text{Ph}_2\text{PCH}_2\text{CH}_2\text{NH}_2$  shows  $^{31}\text{P}$  signal at  $-21$  ppm). Analogous phosphine-substituted compounds such as  $[\text{Fe}_4\text{N}(\text{CO})_{11}(\text{Ph}_2\text{PCH}_2\text{CH}_2\text{OH})]^-$  also have  $\sim 70$  ppm downfield shift in the  $^{31}\text{P}$  NMR resonances. Combustion analysis was performed to confirm bulk purity of each compound. The  $\text{CO}$  absorption bands ( $\nu_{\text{CO}}$ ) in the IR spectra of  $1^-$  and  $2^-$  are slightly shifted to lower energy, relative to those in the unsubstituted cluster  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  because the phosphine ligands are more weakly  $\pi$ -accepting: for  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ , the bands are at 2019 and  $1989 \text{ cm}^{-1}$ ; for  $1^-$ , they are at 1985 and  $1970 \text{ cm}^{-1}$ , and for  $2^-$ , they are at 1959 and  $1943 \text{ cm}^{-1}$  (Fig. S4†).

X-ray diffraction quality crystals for  $\text{Et}_4\text{N-1}$ <sup>18</sup> and  $\text{PPN-2}$ <sup>19</sup> were grown out of layered THF-hexane and saturated toluene solutions, respectively, kept at  $-16^\circ\text{C}$  over 3 or 8 days, respectively (Fig. 1 and Tables S1, S2†). Comparison of Fe–P bond length in  $\text{Et}_4\text{N-1}$  and  $\text{PPN-2}$  reveals that one of the Fe–P bonds in  $2^-$  is slightly elongated (2.210(5) and 2.2070(6) Å), relative to the shorter Fe–P bond in  $1^-$ , which is 2.2066(10) Å. This is likely a steric effect: we have previously noted that Fe–P bond lengths correlate with the size (Tolman cone angle)<sup>20</sup> of a phosphine ligand.<sup>21–23</sup> The Fe(1)–P bond distance (2.2028(6) Å) in similar cluster  $[\text{Fe}_4\text{N}(\text{CO})_{11}(\text{Ph}_2\text{PCH}_2\text{CH}_2\text{OH})]^-$  is also found to be very close to that of  $1^-$ . Replacement of CO by phosphine ligand has a small impact on the Fe–N bond lengths in both  $1^-$  and  $2^-$ . The Fe–N (Fe1–N, Fe4–N, Fe2–N, and Fe3–N) bond lengths in  $1^-$  are 1.780(3), 1.771(3), 1.907(3), and 1.915(3) Å, respectively; and those in  $2^-$  are 1.7857(16), 1.7922(16), 1.9235(15), and 1.9270(15) Å (see ESI for Fe numbering scheme; Chart S1†). The small variations in the structural parameters of  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ ,  $1^-$ , and  $2^-$ , reflect the delocalized bonding which distributes changes in electron density across the metal core.

### Electrochemical experiments

Cyclic voltammograms (CVs) of 0.1 mM solutions of  $1^-$  and  $2^-$  were first measured in anhydrous 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN solution under 1 atm  $\text{N}_2$  (Fig. 2). One reduction event with cathodic peak potential ( $E_{\text{p,c}}$ ) at  $-1.46$  V and anodic peak potential ( $E_{\text{p,a}}$ ) at  $-1.22$  V vs. SCE was observed for  $1^-$  ( $\Delta E_{\text{p}} = 240$  mV). Cyclic

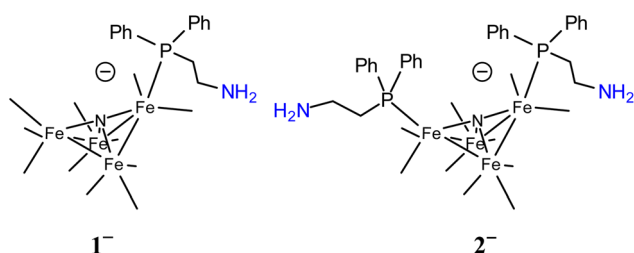


Chart 1 Line drawings of  $1^-$  (left) and  $2^-$  (right). CO ligands are omitted. Atom numbering scheme is in ESI (Chart S1).†

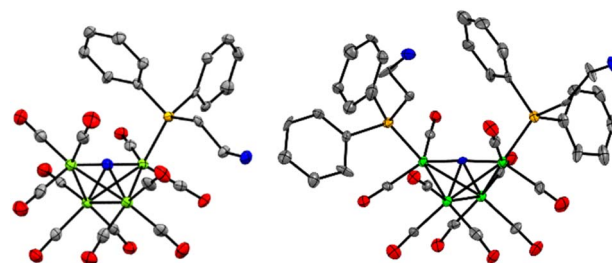


Fig. 1 Solid state structures of (left)  $1^-$  in  $\text{Et}_4\text{N-1}\cdot\text{THF}$ ,<sup>18</sup> and (right)  $2^-$  in  $\text{PPN-2}$ .<sup>19</sup> Gray, blue, green, orange ellipsoids represent C, N, Fe, O and P atoms, respectively. Ellipsoids are shown at 50%; counter cations ( $\text{Et}_4\text{N}^+$  and  $\text{PPN}^+$ ), solvates, and H atoms are omitted for clarity.



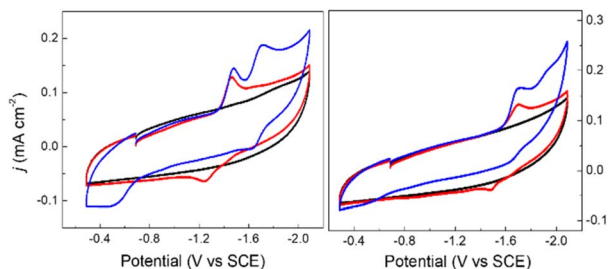



Fig. 2 Cyclic voltammograms of 0.1 mM PPN-1 (left) and PPN-2 (right); in 0.1 M Bu<sub>4</sub>NBF<sub>4</sub> MeCN, under 1 atm of N<sub>2</sub> (red) or CO<sub>2</sub> (blue). Blank recorded under N<sub>2</sub> (black). GC electrode; scan rate: 0.1 V s<sup>-1</sup>.

voltammograms of other mono-substituted clusters, such as [Fe<sub>4</sub>N(CO)<sub>11</sub>(PPh<sub>3</sub>)<sub>3</sub>]<sup>-</sup> and [Fe<sub>4</sub>N(CO)<sub>11</sub>(Ph<sub>2</sub>PCH<sub>2</sub>CH<sub>2</sub>OH)]<sup>-</sup>, showed  $E_{p,c} = -1.49$  V which is consistent with this result. We have previously shown that differential pulse voltammetry (DPV) gives a good estimation of  $E_{1/2}$  when cluster cyclic voltammograms are not fully reversible,<sup>24</sup> and in this case differential pulse voltammetry suggests that  $E_{1/2}(1^{-/2-}) = -1.43$  V (Fig. S8<sup>†</sup>). The electrochemical response of 0.1 mM PPN-2 in 0.1 M Bu<sub>4</sub>NBF<sub>4</sub> MeCN (Fig. 2, right) under 1 atm N<sub>2</sub> shows an irreversible reduction event at  $-1.67$  V vs. SCE, and the differential pulse voltammetry experiment indicates that  $E_{1/2}(2^{-/2-}) = -1.65$  V. The cathodic shift of 220 mV, relative to 1<sup>-</sup>, is consistent with the more electron-rich cluster core after substitution with two phosphine ligands. A linear relationship has previously been demonstrated between  $\nu_{CO}$  and  $E_p$  for [Fe<sub>4</sub>N(CO)<sub>12</sub>]<sup>-</sup> and its substituted analogues.<sup>23,25</sup> Both 1<sup>-</sup> and 2<sup>-</sup> fall on this line as is expected.

For both 1<sup>-</sup> and 2<sup>-</sup>, an analysis of variable scan rate cyclic voltammograms showed a linear variation of peak current density ( $j_p$ ) with scan rate ( $v^{1/2}$ ), although neither compound is rigorously electrochemically irreversible (Fig. S9<sup>†</sup>). The differential pulse voltammetry experiments with 1<sup>-</sup> and 2<sup>-</sup>, were used to support the assignment of each reduction event under N<sub>2</sub> as a one-electron transfer (Fig. S8<sup>†</sup>).

### Reactivity of PPN-1 and PPN-2 with CO<sub>2</sub>

Based on the known chemistry of CO<sub>2</sub> reactions with amines (Scheme 1A),<sup>26</sup> we expected that reaction of 1<sup>-</sup> with CO<sub>2</sub> might afford (PPN)<sub>2</sub>[Fe<sub>4</sub>N(CO)<sub>11</sub>(Ph<sub>2</sub>P(CH<sub>2</sub>)<sub>2</sub>NH<sub>3</sub><sup>+</sup>)]<sub>2</sub>[Fe<sub>4</sub>N(CO)<sub>11</sub>(Ph<sub>2</sub>P(CH<sub>2</sub>)<sub>2</sub>NHCO<sub>2</sub><sup>-</sup>)], which we denote as PPN<sub>2</sub>(1H<sup>+</sup>)(1a<sup>2-</sup>) (Scheme 1B). A reaction of 1<sup>-</sup> with CO<sub>2</sub> might afford PPN [Fe<sub>4</sub>N(CO)<sub>10</sub>(Ph<sub>2</sub>P(CH<sub>2</sub>)<sub>2</sub>NH<sub>3</sub><sup>+</sup>)(Ph<sub>2</sub>P(CH<sub>2</sub>)<sub>2</sub>NHCO<sub>2</sub><sup>-</sup>)], or PPN(2a<sup>-</sup>) (Scheme 1C). We monitored reactions of 1<sup>-</sup> and 2<sup>-</sup> with CO<sub>2</sub> in MeCN using infra-red spectroscopy. There was no change of the  $\nu_{CO}$  absorption bands over 5 h, and this suggests that the cluster core electronic properties are unchanged (Fig. S10<sup>†</sup>). The IR spectra collected under N<sub>2</sub> and CO<sub>2</sub> do show changes in the region of 3300–3800 cm<sup>-1</sup>, and these are consistent with changes in the N–H absorption bands due to carbamate formation (Fig. 3). Under 1 atm CO<sub>2</sub>, sharp absorption bands appear at 3701 and 3594 cm<sup>-1</sup> in the spectra of both 1<sup>-</sup> and 2<sup>-</sup>, and these are consistent with carbamate

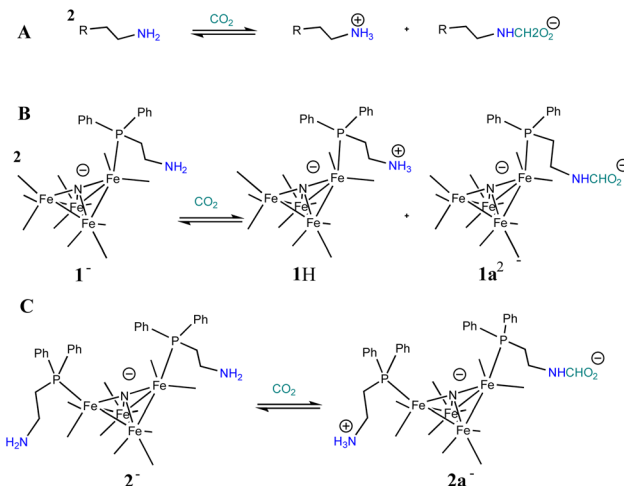

Scheme 1 General known reaction of amines with CO<sub>2</sub> (A); and proposed reaction of 1<sup>-</sup> with CO<sub>2</sub> (B), and of 2<sup>-</sup> with CO<sub>2</sub> (C).

formation.<sup>27,28</sup> To check carbamate under our own conditions, an IR spectrum of dimethylammonium dimethylcarbamate was collected, and shows sharp bands at 3700 and 3595 cm<sup>-1</sup> (Fig. S10<sup>†</sup>, right). For comparison, we also collected the IR spectra of 1<sup>-</sup> and 2<sup>-</sup> under N<sub>2</sub> with 1 equivalent of added benzoic acid (BnCOOH, pK<sub>a</sub> = 21.5 in MeCN),<sup>29</sup> since the BnCOOH should protonate the amine functional groups to afford 1H and 2H, respectively (Scheme 1). These spectra showed very little change relative to those of 1<sup>-</sup> and 2<sup>-</sup>, and this confirms that the sharp bands observed under 1 atm CO<sub>2</sub> are not associated with amine protonation (Fig. S10<sup>†</sup>). Previous studies have observed only small amounts of free amine following reaction with CO<sub>2</sub> in MeCN.<sup>24</sup> Our IR analysis is in agreement with that result, although precise concentrations cannot be calculated from the acquired spectra. We therefore estimate the equilibrium constant ( $K_{eq}$ ) for CO<sub>2</sub> binding as described in Scheme 1A and B to be high, with  $K_{eq} > 10$ .

We will first discuss the electrochemical data associated with the CO<sub>2</sub> reactivity of PPN-1. As mentioned in the previous

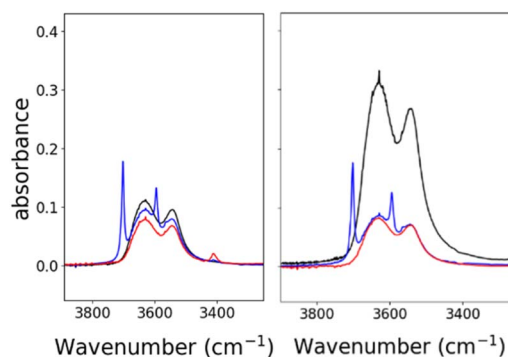


Fig. 3 IR spectra showing N–H absorption bands for: 0.7 mM 1<sup>-</sup> (left) and 2<sup>-</sup> (right), both in MeCN. Under 1 atm of N<sub>2</sub> (black), under 1 atm CO<sub>2</sub> (blue), and with 0.7 mM of benzoic acid under 1 atm N<sub>2</sub> (red). Full spectral ranges are shown in Fig. S10<sup>†</sup>.



paragraph, there is no change to the  $\nu_{\text{CO}}$  absorption bands for  $\mathbf{1}^-$  upon reaction with  $\text{CO}_2$ ; this suggests that the cluster core electronic properties are unchanged, and therefore, that the  $E_{1/2}$  values for  $\mathbf{1H}^{0/-}$  and  $\mathbf{1a}^{2-/3-}$  should be equivalent to  $E_{1/2}(\mathbf{1}^{-/2-})$ . Cyclic voltammetry measurements were performed in 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN saturated with  $\text{CO}_2$  (Fig. 2, blue). Under these conditions, the quasi-reversible cyclic voltammogram of  $\mathbf{1}^-$  under 1 atm  $\text{N}_2$  becomes an irreversible event at  $-1.43$  V, and a new reversible wave at more cathodic potential ( $E_{1/2} = -1.62$  V vs. SCE,  $\Delta E_p = 100$  mV) was observed (Fig. 2, left). No change in the irreversibility was observed when the scan rate is faster (Fig. S11†). Since the redox event for  $\mathbf{1H}^{0/-}$  and  $\mathbf{1a}^{2-/3-}$  is irreversible under  $\text{CO}_2$ , we cannot use this to calculate  $K_b$  for the reaction shown in Scheme 1B.

Cyclic voltammograms collected under  $\text{CO}_2$  at intervals from 1 to 18 min showed a gradual change in the cyclic voltammograms of  $\mathbf{1}^-$  over 20 min, after addition of  $\text{CO}_2$  and this gradual change is consistent with the knowledge that reactions of amines with  $\text{CO}_2$  to afford carbamate are relatively slow (Fig. 4, left).<sup>30,31</sup> Based on the IR data showing no change to  $\nu_{\text{CO}}$ , we tentatively assigned the redox event at  $-1.43$  V to overlapping reduction of both  $\mathbf{1H}$  and  $\mathbf{1a}^-$ . When the solution of  $\mathbf{1}^-$  was purged with  $\text{N}_2$ , the redox event at  $-1.67$  V diminished, which is further consistent with its assignment as related to formation of  $\mathbf{1H}$  and  $\mathbf{1a}^-$ . A differential pulse voltammetry experiment performed under 1 atm  $\text{CO}_2$  on a solution containing 0.1 mM  $\text{Me}_{10}\text{Fc}$  and 0.1 mM  $\mathbf{1}^-$  showed two reduction events associated with  $\mathbf{1H}$  and  $\mathbf{1a}^-$ , consistent with the cyclic voltammetry data (Fig. S11†).

The cyclic voltammogram of  $\mathbf{1}^-$  collected under 1 atm  $\text{CO}_2$  also shows an oxidative process at  $-0.5$  V (Fig. 2), and this is consistent with the location where we usually observe oxidation of an intermediate catalyst hydride formed from reduction of clusters such as  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  in the presence of protons: specifically it is equivalent to oxidation of  $[\text{H}-\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ , and in this case it should be oxidation of  $(\text{H}-\mathbf{1H})^-$  or of  $(\text{H}-\mathbf{1a})^{2-}$ , or an overlapping oxidation of both. The observation of a hydride oxidation event, for oxidation of  $(\text{H}-\mathbf{1H})$  and  $(\text{H}-\mathbf{1a})^{2-}$ , at  $-0.5$  V


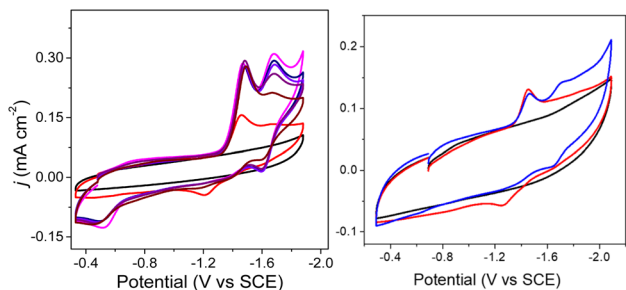


Fig. 4 Left: cyclic voltammograms of 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN solution under 1 atm  $\text{N}_2$  (black), with 0.1 mM  $\mathbf{1}^-$  (red), and under 1 atm  $\text{CO}_2$  over 16 min where  $\text{PPN}_2(\mathbf{1H})(\mathbf{1a})$  is formed (pink). The solution was then purged with  $\text{N}_2$ , which initiates slow desorption of  $\text{CO}_2$ ; as seen in scans with decreased current response, recorded at 1, 6, 11, and 20 min after the  $\text{N}_2$  purge (other colors). Right: cyclic voltammograms under 1 atm  $\text{N}_2$  of 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN (black), 0.1 mM  $\mathbf{1}^-$  (red), and 0.1 mM  $\mathbf{1}^-$  with 0.11 mM benzoic acid (blue).

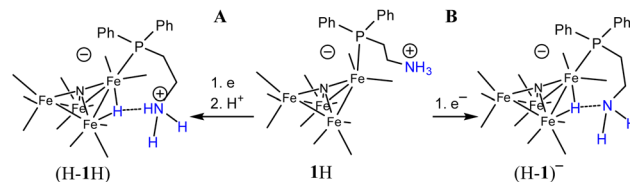

Scheme 2 Presentation of possible H-bond stabilization that enables observation of  $(\text{H}-\mathbf{1H})^{0/-}$  or  $(\text{H}-\mathbf{1a})^{2-}$ , couple at  $-1.63$  V. (A) Proton source is from bulk solution; (B) proton source for hydride formation is the amine SCS group.

suggests that the reversible redox event with  $E_{1/2} = -1.62$  V could be the redox couple associated with  $(\text{H}-\mathbf{1H})^{0/-}$  or  $(\text{H}-\mathbf{1a})^{2-/3-}$ , or both. To test this hypothesis, we collected cyclic voltammograms and differential pulse voltammograms of  $\mathbf{1}^-$  under 1 atm  $\text{N}_2$  and in the presence of a proton source (Fig. 4 and S11†). The  $\text{p}K_a$  of  $\mathbf{1H}$  should be about 18.4 in MeCN, based on comparison with the known acidity of alkylamines,<sup>32</sup> and so we investigated the possibility that  $\mathbf{1H}$  serves as a proton source for cluster-hydride formation by employing an acid that has  $\text{p}K_a$  matched to the SCS amine group. Recorded cyclic voltammograms of 0.1 mM  $\mathbf{1}^-$  in 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN under 1 atm  $\text{N}_2$  with 1 equivalent of  $\text{BnCOOH}$  show an irreversible reduction event at  $-1.43$  V and a reversible wave at  $E_{1/2} = -1.62$  V,  $\Delta E_p = 130$  mV (Fig. 4). In addition, an oxidation event at  $-0.5$  V is observed. This experiment shows that the redox couple at  $E_{1/2} = -1.62$  V is associated with a proton source and supports its assignment to reversible reduction of the hydride intermediates that are formed at  $-1.43$  V.

We have not previously observed reduction of  $[\text{H}-\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ , and propose that stabilization of  $(\text{H}-\mathbf{1H})$  and  $(\text{H}-\mathbf{1a})^{2-}$  by the SCS amine (or ammonium, or carbamate) functional group is responsible for suppressing reaction of the hydride with a substrate (Scheme 2). The electron rich nature of the hydride allows for the H-bond interaction between it and the amine, or ammonium. The carbamate is less likely to interact with hydride. In prior work, a linear relationship between  $E_{1/2}$  and  $\Delta G_{\text{Hyd}}$  has been established for a series of iron carbonyl clusters.<sup>33</sup> We can therefore estimate the hydricities of  $(\text{H}-\mathbf{1H})^-$  and  $(\text{H}-\mathbf{2H})^-$  to be 46 and 43 kcal mol<sup>-1</sup> respectively. The existence of the oxidation wave at  $-0.5$  V even under 1 atm  $\text{CO}_2$ , further supports the hypothesis of H-bond stabilization of hydride intermediates  $(\text{H}-\mathbf{1H})$  and  $(\text{H}-\mathbf{1a})^{2-}$ , since our prior work has shown that the oxidation of  $[\text{H}-\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  is usually observed under  $\text{N}_2$  but not under  $\text{CO}_2$ .<sup>34</sup> H-bonding between hydride and an appended functional group is well-established and has been characterized in several prior cases, either crystallographically<sup>35</sup> or spectroscopically.<sup>36-38</sup>

### Electrochemical reactivity of PPN-2 with $\text{CO}_2$

The  $E_{1/2}$  values for  $\mathbf{2a}^-$  are expected to be roughly equivalent to  $E_{1/2}(\mathbf{2}^{-/2-}) = -1.67$  V, since the  $\nu_{\text{CO}}$  absorption bands for  $\mathbf{2}^-$  and  $\mathbf{2a}^-$  were observed at the same energy. Electrochemical measurements performed under 1 atm  $\text{CO}_2$ , with solutions containing 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN and 0.1 mM  $\mathbf{2}^-$  show an



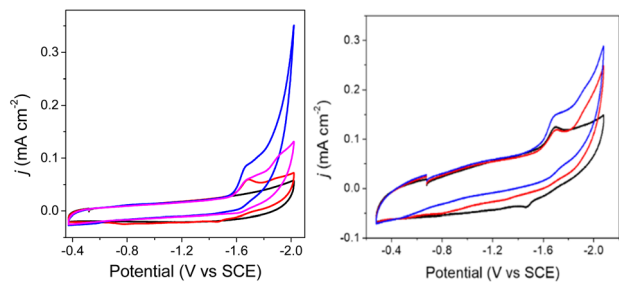


Fig. 5 Cyclic voltammograms of 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN solutions. Left: under  $\text{N}_2$  (black), with 0.1 mM  $2^-$  under 1 atm  $\text{N}_2$  (red), with 0.1 mM  $2^-$  under 1 atm  $\text{CO}_2$  (blue), and after purging the  $\text{CO}_2$  saturated solution with  $\text{N}_2$  for 10 min, decreasing the current (pink). Right: with 0.1 mM  $2^-$  under 1 atm  $\text{N}_2$  (black) and with added 0.5 mM  $\text{OMeBSulfH}$  (red), and under 1 atm  $\text{CO}_2$  (blue). Blank cyclic voltammograms for 0.5 mM  $\text{OMeBSulfH}$  (where  $2^-$  is absent) are shown in Fig. S12.†

increase in current density at  $-1.67$  V, and a small reduction feature at  $-1.92$  V, which we assign as the  $(\text{H-2a})^{-2-}$  couple (Fig. 2, right), consistent with our assignments made for  $(\text{H-1a})^{-2-}$  (Fig. 2, left). Oxidation of putative  $(\text{H-2a})^-$  is also observed as a low current density feature of this cyclic voltammogram on the return oxidative scan at  $-0.49$  V. To confirm that the features at  $-1.92$  and  $-0.49$  V are associated with redox chemistry of *in situ*-generated  $(\text{H-2a})^-$ , we performed a cyclic voltammetry experiment on solutions containing  $2^-$  and  $\text{OMeBSulfH}$  (Fig. 5, right). The stronger acid,  $\text{BnCOOH}$  was used in a similar study for  $1^-$  (Fig. 4) but cannot be used here since  $\text{H}_2$  would be generated by the GC electrode at  $-1.92$  V. The features at  $-1.92$  and at  $-0.49$  V were observed, but both have relatively lower current densities compared with the equivalent events associated with the redox events assigned to  $(\text{H-1H})$  and  $(\text{H-1a})^{2-}$  (Fig. 4, right): this suggests that stabilization of  $(\text{H-2a})^-$  is not as efficient as stabilization of  $(\text{H-1H})$  and  $(\text{H-1a})^{2-}$ . Further, this observation implies that hydride transfer (HT) from  $(\text{H-1H})$  and/or  $(\text{H-1a})^{2-}$  to  $\text{CO}_2$  should be inefficient (resulting in no or minimal formate formation), whereas HT from  $(\text{H-2a})^-$  to  $\text{CO}_2$  might be possible.

### Electrolysis and product quantification

Controlled potential electrolysis (CPE) experiments were performed to determine whether any products of  $\text{CO}_2$  or proton reduction are being formed during the cyclic voltammetry experiments, and upon reductive electrolysis of 0.1 mM  $1^-$  or  $2^-$  under 1 atm  $\text{CO}_2$ . The CPE experiments were followed by analysis of the head space using gas chromatography with thermal conductivity detector (GC-TCD) to quantify  $\text{CO}$  or  $\text{H}_2$ , and analysis of the solution using high-performance liquid chromatography (HPLC) to quantify formate. We chose *p*-methoxy benzene sulfonium ( $\text{OMeBSulfH}$ ,  $\text{p}K_{\text{a}}(\text{MeCN}) = 25.9$ ),<sup>39</sup> for the CPE experiments since it will not make  $\text{H}_2$  in a background reaction with the glassy carbon (GC) working electrode.

CPE experiments with  $1^-$  were performed at and near the peak potential for reduction of  $1^-$ , at  $-1.40$  V, with and without added 5 mM  $\text{OMeBSulfH}$ , under 1 atm  $\text{CO}_2$ . In all cases, no product resulting from a faradaic process was detected above

the detection limits for  $\text{CO}$ ,  $\text{H}_2$ , or formate (Table S3 and Fig. S13–S15†). We did observe some  $\text{CO}$  formation which we attribute to cluster decomposition based on the decrease in intensity of the  $\text{CO}$  absorption bands in the IR spectrum taken after the CPE experiment (Fig. S15†). In addition, when a CPE experiment was performed with  $1^-$  using  $^{13}\text{CO}_2$ , no  $\text{CO}_2$  reduction products were observed in a  $^{13}\text{C}$ -NMR spectrum collected following the CPE (Fig. S16†). The CPE results obtained with  $1^-$  suggest that stabilization of the  $(\text{H-1})^-$  intermediate we observed in the cyclic voltammetry experiments, is preventing a HT reaction under catalytic conditions.

CPE performed with 0.1 mM  $2^-$  and 5 mM  $\text{OMeBSulfH}$ , at various cathodic potentials between  $-1.54$  and  $-1.74$  V produced a mixture of products for which the relative amounts varied with applied potential (Fig. 6 and Table S3†). These potentials were selected based on their position near the  $E_p$ . The maximum yield of formate produced was a faradaic efficiency (FE) of 51% at  $-1.74$  V, and  $\text{H}_2$  and  $\text{CO}$  were also observed at this potential with FE of 14% and 24%, respectively (Calculation S1†). IR spectra recorded before and after the CPE experiment suggest that  $2^-$  is 18% decomposed over the 20 min experiment and that the likely source of  $\text{CO}$  is ligands from the cluster (Fig. S15†). No  $\text{CO}_2$  reduced products were detected when blank CPE experiments were carried out in the absence of  $2^-$  under 1 atm  $\text{CO}_2$ . CPE experiments were also run with the used electrodes from CPE experiments containing  $2^-$ , and those also produced no carbon-containing products. CPE experiments carried out under 1 atm of  $^{13}\text{CO}_2$  atmosphere showed that formate was produced, using  $^{13}\text{C}$ -NMR spectroscopy (Fig. S17†). No  $^{13}\text{CO}$  was observed.

Taken together the results of the CPE experiments with  $1^-$  and  $2^-$  suggest that stabilization of the catalyst hydride by the SCS amine group is hindering HT so that both  $\text{H}_2$  and formate formation are suppressed, and instead some catalyst decomposition occurs, especially for  $1^-$  where the HT is most hindered. The cyclic voltammetry experiments described earlier are consistent with the CPE results (Fig. 4). In particular, the suppression of  $\text{H}_2$  at potentials as negative as  $-1.67$  V in the presence of organic acids is good evidence for suppression of the HT reaction. One possible reason that HT is more effectively suppressed for  $1^-$  is that the reduction potential,  $-1.43$  V, is 220 mV less reducing than for  $2^-$  at  $-1.65$  V. Another possible

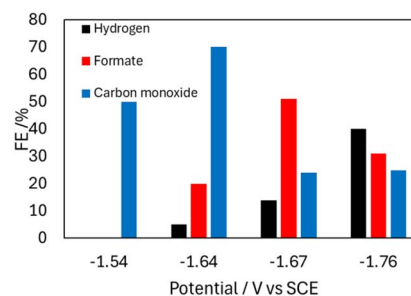


Fig. 6 Bar graph showing the product profile relative to  $E_{\text{app}}$ , from CPE experiments performed with 0.1 mM  $2^-$  in 0.1 M  $\text{Bu}_4\text{NBF}_4$  MeCN solution with 5 mM  $\text{OMeBSulfH}$  under 1 atm  $\text{CO}_2$  over 20 min.



reason for the effective HT suppression in  $1^-$  is the orientation of the primary amine functional group: in the solid-state structure of  $1^-$  the amine is directed down toward the hydride active site because there is more space for the Ph rings above the cluster (Fig. 1). In the solid-state structure of  $2^-$ , the presence of two  $\text{PPh}_2(\text{EtNH}_2)$  substituents generates more steric crowding so that the amine groups (which are smaller than the Ph rings) are directed more away from the site of the hydride (Fig. 1).


### Reaction mechanism under catalytic conditions

The foregoing mechanistic investigations performed using IR spectroscopy and cyclic voltammetry, combined with the identification of products using CPE experiments, lead us to propose a mechanism for  $\text{CO}_2$  reduction which involves a series of chemical and ET steps including amine reactions with  $\text{CO}_2$  and both inter- and intra-molecular PT reactions and HT to afford formate (Scheme 3). There are some ambiguities with the proposed mechanism, which include the origin of the proton that leads to formation of  $(\text{H-}2\text{a})^-$  (Scheme 3) and the origin of the  $\text{CO}_2$  substrate involved in HT, which could be released from the amine SCS or it could be from dissolved  $\text{CO}_2$  in solution. This latter question can be explored further by measuring the observed rate constant of formate formation ( $k_{\text{obs}}$ ), since this would be an approximation of the rate-determining HT step in the catalytic cycle (Scheme 3). If this rate constant is higher than we have observed for formate formation by  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ , that would suggest  $\text{CO}_2$  that is locally released from the SCS amine functional group might be involved in catalysis. We have previously reported  $k_{\text{obs}}$  for formate formation in MeCN solution from limiting current analysis as  $k_{\text{obs}} = 10 \text{ s}^{-1}$ .<sup>17</sup>

To elucidate the effect of the SCS amine functional groups on the mechanism and rate of formate production, we analysed the limiting current observed in cyclic voltammetry experiments performed with  $2^-$  and an excess of  $\text{CO}_2$  substrate. The catalytic plateau current,  $j_c$  generated by a homogenous electrocatalyst in pure kinetic regime with excess substrate is described by eqn (1):<sup>40,41</sup>

$$j_c = nF[\text{cat}]k_{\text{obs}}^{1/2}D^{1/2} \times 10^3 \quad (1)$$

where  $j_c$  is the background-corrected plateau current density ( $\text{mA cm}^{-2}$ ),  $n = 2$  for number of electrons for  $\text{CO}_2$  reduction to formate,  $F$  is the Faraday's constant,  $[\text{cat}]$  is  $[2^-]$  ( $\text{mol cm}^{-3}$ ),  $D = 9.5 \times 10^{-6} \text{ cm}^2 \text{ s}^{-1}$  (Fig. S9<sup>†</sup>), and  $k_{\text{obs}}$  is the observed rate constant ( $\text{s}^{-1}$ ). We first measured the order of the catalytic reaction with respect to the concentration of the proton source in CPE, which is  $^{\text{OMe}}\text{BSulfH}$ , and to  $[2^-]$ . When a solution of  $0.1 \text{ mM } 2^-$  in  $0.1 \text{ M Bu}_4\text{NBF}_4 \text{ MeCN}$  under  $1 \text{ atm CO}_2$  was titrated with increasing amounts of  $^{\text{OMe}}\text{BSulfH}$ , the  $2^-/2a^-$  redox couple became irreversible after 1 equivalent of  $^{\text{OMe}}\text{BSulfH}$  had been added. Addition of further  $^{\text{OMe}}\text{BSulfH}$  did not increase  $j_c$  at  $-1.67 \text{ V}$ . This indicates zero-order dependence of  $k_{\text{obs}}$  on  $[^{\text{OMe}}\text{BSulfH}]$  (Fig. 7). A solution containing  $1 \text{ mM } ^{\text{OMe}}\text{BSulfH}$  under  $1 \text{ atm CO}_2$  was titrated with  $0.025 \text{ mM}$  up to  $0.2 \text{ mM}$  of  $2^-$ , and we observed that  $j_c$  increases linearly at  $-1.67 \text{ V}$ , pointing toward a first-order dependence of the catalytic reaction on  $[2^-]$  (Fig. 7). Measurement of  $k_{\text{obs}}$  was performed from the limiting current analysis (Calculation S2<sup>†</sup> and Fig. 7), and afforded  $k_{\text{obs}} = 22 \text{ s}^{-1}$ . A correction for the  $\text{FE}(\text{HCOO}^-)$  was applied to give a rate constant of  $k_{\text{obs}}(\text{FE}) = 7.3 \text{ s}^{-1}$  (Calculation S3<sup>†</sup>). This rate constant is on the same order of magnitude compared to a previous measurement for the rate constant measured for formate formation by  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$ . This result supports a proposal that  $\text{CO}_2$  substrate is derived from dissolved  $\text{CO}_2$  in solution. We note that 18% decomposition of  $2^-$  was observed in CPE experiments performed over 20 min but

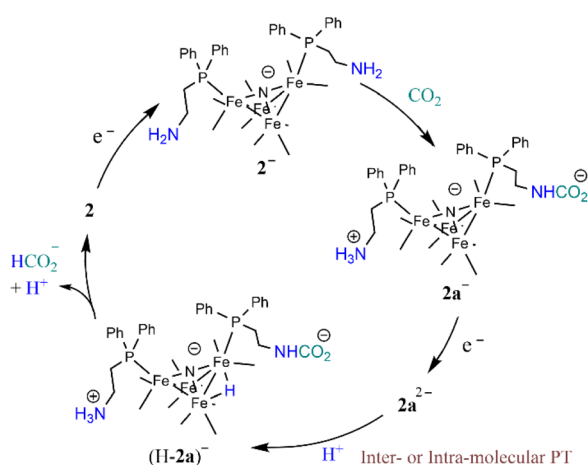

Scheme 3 Proposed mechanism for  $\text{CO}_2$  reduction to formate by  $2^-$ .

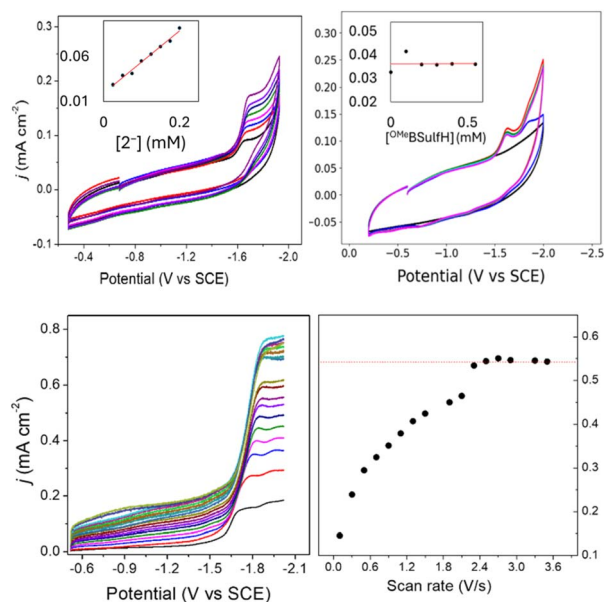


Fig. 7 Top: cyclic voltammograms in  $0.1 \text{ M Bu}_4\text{NBF}_4 \text{ MeCN}$  solution: (left)  $1 \text{ mM } ^{\text{OMe}}\text{BSulfH}$ , with added  $2^-$  at  $0.025, 0.05, 0.075, 0.1, 0.125, 0.15, 0.175,$  and  $0.2 \text{ mM}$ . Inset: plot of  $j_c$  vs.  $[2^-]$  read at  $-1.67 \text{ V}$ ; (right)  $0.1 \text{ mM } 2^-$ , with added  $^{\text{OMe}}\text{BSulfH}$ . Inset: plot of  $j_c$  vs.  $[^{\text{OMe}}\text{BSulfH}]$  read at  $-1.67 \text{ V}$ . GC electrode; scan rate:  $100 \text{ mV s}^{-1}$ . Bottom: (left) forward cyclic voltammogram traces of  $0.09 \text{ mM } 2^-$  in  $0.1 \text{ M Bu}_4\text{NBF}_4 \text{ MeCN}$  with  $5 \text{ mM } ^{\text{OMe}}\text{BSulfH}$  under  $1 \text{ atm CO}_2$  at scan rates  $0.1, 0.3, 0.5, 0.7, 0.9, 1.1, 1.3, 1.5, 1.9, 2.1, 2.3, 2.5, 2.7, 2.9, 3.3,$  and  $3.5 \text{ V s}^{-1}$ ; and (right) plot of  $j_{\text{max}}$  vs. scan rate ( $v$ ) read at  $-1.95 \text{ V}$ .



the CV measurement of rate is performed over about 1 min where very little decompositions is expected.

## Conclusions

The role of SCS amine functional groups on catalyst-hydride formation and on HT reactions has been modelled in this report. Two synthetic models for an iron catalyst were prepared, containing one amine SCS group ( $1^-$ ) or two amine SCS groups ( $2^-$ ), and these amine groups were positioned near the surface active site of the catalyst with alkyl linkers. IR spectroscopy confirms the reaction of the appended amines with  $\text{CO}_2$  to form carbamate and ammonium. A mechanistic study, employing IR spectroscopy, cyclic voltammetry, and CPE results, determined that the SCS amine group in  $1^-$  has a highly stabilizing effect on the catalyst-hydride intermediate so that formate formation is completely suppressed. The structure of  $2^-$  appears to be less rigid so that stabilization of the catalyst-hydride intermediate, ( $\text{H-2a}^-$ ), is only partially effective, according to both the cyclic voltammetry and CPE data. Formate formation by  $2^-$  is therefore only partially suppressed and observed with 51% FE. The rate of formate formation by  $2^-$  and  $[\text{Fe}_4\text{N}(\text{CO})_{12}]^-$  are on the same order of magnitude which suggests that the substrate for catalysis by  $2^-$  is not related to any behavior of the SCS carbamate functional group.

## Data availability

Crystallographic data for Et<sub>4</sub>N-1·THF and PPN-2 have been deposited at the Cambridge Crystallographic Data Centre under 2391540 and 2391541 and can be obtained from <https://doi.org/10.5517/ccdc.csd.cc2l8lgy> and <https://doi.org/10.5517/ccdc.csd.cc2l8lhz>.

## Author contributions

The manuscript was written through contributions of all authors.

## Note added after first publication

This article replaces the version published on 13 February 2025 in which the CSD Communications <https://doi.org/10.5517/ccdc.csd.cc2l8lgy> and <https://doi.org/10.5517/ccdc.csd.cc2l8lhz> had not been cited for structures 2391540 and 2391541, respectively.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This manuscript is based upon work supported by the Department of Energy, Office of Science, Basic Energy Sciences with award number DE-SC0016395. Our initial interest in amine functional groups arose from work in the Center for

Direct Conversion of Captured  $\text{CO}_2$  to Fuels and Chemicals, funded by the University of California Office of the President, National Laboratory Fees Research Fees Program Award L22CR4468, and we acknowledge that group for stimulating discussions.

## Notes and references

- 1 M. W. Drover, *Chem. Soc. Rev.*, 2022, **51**(6), 1861–1880, DOI: [10.1039/d2cs00022a](https://doi.org/10.1039/d2cs00022a).
- 2 T. L. Soucy, W. S. Dean, J. Zhou, K. E. Rivera Cruz and C. C. L. McCrory, *Acc. Chem. Res.*, 2022, **55**, 252–261, DOI: [10.1021/acs.accounts.1c00633](https://doi.org/10.1021/acs.accounts.1c00633).
- 3 S. Ren, D. Joulié, D. Salvatore, K. Torbensen, M. Wang, M. Robert and C. P. Berlinguette, *Science*, 2019, **365**(6451), 367–369, DOI: [10.1126/science.aax4608](https://doi.org/10.1126/science.aax4608).
- 4 C. Costentin, S. Drouet, M. Robert and J.-M. Savéant, *Science*, 2012, **338**, 90–94.
- 5 C. T. Supuran, *Biochem. J.*, 2016, **473**, 2023–2032.
- 6 S. Thoms, *J. Theor. Biol.*, 2002, **215**, 399–404.
- 7 Y. Nicolet and J. C. Fontecilla-Camps, *J. Biol. Chem.*, 2012, **287**, 13532–13540.
- 8 J. Duan, S. Mebs, K. Laun, F. Wittkamp, J. Heberle, T. Happe, E. Hofmann, U. Apfel, M. Winkler, M. Senger, M. Haumann and S. T. Stripp, *ACS Catal.*, 2019, **9**, 9140–9149.
- 9 A. K. Buckley, M. Lee, T. Cheng, R. V. Kazantsev, D. M. Larson, W. A. Goddard III, D. F. Toste and F. M. Toma, *J. Am. Chem. Soc.*, 2019, **141**, 7355–7364.
- 10 A. Thevenon, A. Rosas-Hernández, A. M. Fontani Herreros, T. Agapie and J. C. Peters, *ACS Catal.*, 2021, **11**, 4530–4537.
- 11 Z. Han, R. Kortlever, H. Chen, J. C. Peters and T. Agapie, *ACS Cent. Sci.*, 2017, **3**, 853–859.
- 12 S. Patra, S. Bhunia, S. Ghosh and A. Dey, *ACS Catal.*, 2024, **14**, 7299–7307.
- 13 A. Chapovetsky, M. Welborn, J. M. Luna, R. Haiges, T. F. Miller and S. C. Marinescu, *ACS Cent. Sci.*, 2018, **4**, 397–404.
- 14 S. Roy, B. Sharma, J. Pøcaut, P. Simon, M. Fontecave, P. D. Tran, E. Derat and V. Artero, *J. Am. Chem. Soc.*, 2017, **139**, 3685–3696.
- 15 M. H. Rønne, D. Cho, M. R. Madsen, J. B. Jakobsen, S. Eom, É. Escudø, H. C. D. Hammershøj, D. U. Nielsen, S. U. Pedersen, M.-H. Baik, T. Skrydstrup and K. Daasbjerg, *J. Am. Chem. Soc.*, 2020, **142**, 4265–4275.
- 16 A. Taheri, C. R. Carr and L. A. Berben, *ACS Catal.*, 2018, **8**, 5787–5793.
- 17 A. Taheri and L. A. Berben, *ACS Catal.*, 2015, **5**, 7140–7151.
- 18 S. Pattanayak, R. Siegel, Y. Liu, J. Fettinger and L. Berben, *CCDC 2391540: Experimental Crystal Structure Determination*, 2025, DOI: [10.5517/ccdc.csd.cc2l8lgy](https://doi.org/10.5517/ccdc.csd.cc2l8lgy).
- 19 S. Pattanayak, R. Siegel, Y. Liu, J. Fettinger and L. Berben, *CCDC 2391541: Experimental Crystal Structure Determination*, 2025, DOI: [10.5517/ccdc.csd.cc2l8lhz](https://doi.org/10.5517/ccdc.csd.cc2l8lhz).
- 20 C. A. Tolman, *Chem. Rev.*, 1977, **77**, 313–348.
- 21 N. D. Loewen, E. J. Thompson, M. Kagan, C. L. Banales, T. W. Myers, J. C. Fettinger and L. A. Berben, *Chem. Sci.*, 2016, **7**, 2728–2735.



- 22 N. D. Loewen and L. A. Berben, *Inorg. Chem.*, 2018, **58**, 16849–16857.
- 23 N. D. Loewen, S. Pattanayak, R. Herber, J. C. Fettinger and L. A. Berben, *J. Phys. Chem. Lett.*, 2021, **12**, 3066–3073.
- 24 K. Y. C. Lee, D. E. Polyansky, D. C. Grills, M. Aceves, J. C. Fettinger and L. A. Berben, *ACS Org. Inorg. Au*, 2024, **4**(6), 649–657, DOI: [10.1021/acsoiginorgau.4c00041](https://doi.org/10.1021/acsoiginorgau.4c00041).
- 25 S. Pattanayak, N. D. Loewen and L. A. Berben, *Inorg. Chem.*, 2023, **62**, 1919–1925.
- 26 K. Masuda, Y. Ito, M. Horiguchi and H. Fujita, *Tetrahedron*, 2005, **61**(1), 213–229, DOI: [10.1016/j.tet.2004.10.033](https://doi.org/10.1016/j.tet.2004.10.033).
- 27 J. T. Chen and W. R. Benson, *J. - Assoc. Off. Anal. Chem.*, 1966, **49**, 412–452.
- 28 R. K. Khanna and M. H. Moore, *Spectrochim. Acta, Part A*, 1999, **55**, 961–967.
- 29 A. Kütt, S. Tshepelevitsh, M. Lökov, I. Kaljurand, S. Selberg and I. Leito, *Eur. J. Org. Chem.*, 2021, **9**, 1407–1419.
- 30 X. Wang, W. Conway, D. Fernandes, G. Lawrance, R. Burns, G. Puxty and M. Maeder, *J. Phys. Chem. A*, 2011, **115**, 6405–6412.
- 31 W. Conway, X. Wang, D. Fernandes, R. Burns, G. Lawrance, G. Puxty and M. Maeder, *Environ. Sci. Technol.*, 2012, **46**, 7422–7429.
- 32 S. Tshepelevitsh, A. Kütt, M. Lökov, I. Kaljurand, J. Saame, A. Heering, P. G. Plieger, R. Vianello and I. Leito, *Eur. J. Org. Chem.*, 2019, **40**, 6735–6748.
- 33 N. D. Loewen, T. V. Neelakantan and L. A. Berben, *Acc. Chem. Res.*, 2017, **50**(9), 2362–2370.
- 34 M. D. Rail and L. A. Berben, *Inorg. Chem.*, 2012, **51**, 1480–1488.
- 35 M. E. Carroll, B. E. Barton, T. B. Rauchfuss and P. J. Carroll, *J. Am. Chem. Soc.*, 2012, **134**(45), 18843–18852, DOI: [10.1021/ja309216v](https://doi.org/10.1021/ja309216v).
- 36 G. A. Silant'ev, O. A. Filippov, P. M. Tolstoy, N. V. Belkova, L. M. Epstein, K. Weisz and E. S. Shubina, *Inorg. Chem.*, 2013, **52**(4), 1787–1797, DOI: [10.1021/ic301585k](https://doi.org/10.1021/ic301585k).
- 37 E. S. Shubina, N. V. Belkova, A. N. Krylov, E. V. Vorontsov, L. M. Epstein, D. G. Gusev, M. Niedermann and H. Berke, *J. Am. Chem. Soc.*, 1996, **118**(5), 1105–1112, DOI: [10.1021/ja953094z](https://doi.org/10.1021/ja953094z).
- 38 S. Zhang, A. M. Appel and R. M. Bullock, *J. Am. Chem. Soc.*, 2017, **139**, 7376–7387.
- 39 K. Izutsu, Acid-Base Dissociation Constants in Dipolar Aprotic Solvents, *IUPAC Chemical Data Series, No. 35*, Blackwell Scientific, Boston, USA, 1990.
- 40 J.-M. Savéant, *Elements of Molecular and Biomolecular Electrochemistry*, John Wiley & Sons, Hoboken, USA, 2006.
- 41 J.-M. Savéant, *Angew. Chem., Int. Ed.*, 2019, **58**(7), 2125–2128, DOI: [10.1002/anie.201812375](https://doi.org/10.1002/anie.201812375).

