

Cite this: *Chem. Sci.*, 2025, 16, 10642 All publication charges for this article have been paid for by the Royal Society of Chemistry

Synergistic effects of atomically precise Au-based bimetallic nanocluster on energy-related small molecule catalysis

Yuanxin Du, * Yi Fang, Pei Wang and Manzhou Zhu *

Utilizing renewable sources to convert small-molecule energy carriers (such as nitrogen, carbon dioxide, water, or oxygen) into high value-added chemicals and fuels is of great significance. Rational design of the catalyst is the key to achieving efficient catalytic performance. Atomically precise metal nanoclusters (NCs) exhibit the advantages of high atomic economy, distinctive discrete electronic energy, and homogeneity in size, composition, structure, and surface environment, not only offering extraordinary catalytic activity but also providing the opportunity to reveal the reaction mechanism. In the metal NC family, Au-based NCs have attracted widespread and sustained interest due to their simple preparation, high stability, easy functionalization, and especially their unique catalytic activity, which once provoked a "gold rush" in academia. The synergistic effect between different metal atoms is regarded as an effective strategy to achieve enhanced catalytic performance, but the underlying mechanism is a puzzle. Recently, abundant, diverse and adjustable atomically precise Au-based bimetallic NCs (doped with Ag, Cu, Pt, Pd, Cd, Hg, Ir etc.) have emerged, which not only provide a bank of materials for highly active catalysts, but also provide feasibility for revealing synergistic effects at the atomic level. This perspective briefly introduces the common synthesis strategy and structural characteristics of atomically precise Au-based bimetallic NCs, summarizes recent advances in their synergistic catalysis in energy-related small-molecule conversion, and proposes insights and advice for future breakthroughs in this field.

Received 12th February 2025
Accepted 26th April 2025

DOI: 10.1039/d5sc01108f

rsc.li/chemical-science

1. Introduction

In order to actively tackle the current increasingly severe energy crisis and environmental problems, the search for renewable, clean and environmentally friendly new energy resources has become the consensus and the focus of joint efforts of all countries in the world.^{1–4} Therefore, the catalytic reaction of small molecules related to new energy storage and conversion technologies, such as the hydrogen evolution reaction (HER), the oxygen evolution reaction (OER), the oxygen reduction reaction (ORR), fuel small-molecule oxidation reactions, the carbon dioxide reduction reaction (CO₂RR), and synthetic ammonia reactions has aroused great interest and attention in academia and industry.⁵ Although some breakthroughs have been achieved after decades of effort and development, these catalytic reactions still face some bottlenecks that need to be overcome. For example, the electrocatalytic water splitting technique for hydrogen production involving HER and OER theoretically requires an applied voltage of 1.23 V in the

standard state (25 °C, 1 atm).^{6,7} However, in actual situations, the applied voltage is much higher than the theoretical value. The main reason for this serious deviation from the theoretical voltage phenomenon is that the activity of existing catalysts is not high enough to overcome the reaction energy barrier that OER and HER need to cross as well as solution resistance and contact resistance.^{8–10} For full-cells and metal-air batteries, the critical process is ORR, which not only faces the limitation of sluggish kinetics but also faces the problem of selectivity, because it has two possible pathways: one undergoes a 4-electron transfer step to achieve the complete conversion of O₂ to H₂O, and the other is a 2-electron reaction pathway to generate H₂O₂.^{11–13} For CO₂RR, the difficulty in CO₂ activation due to its chemical inertness and the poor product selectivity due to various possible reduction pathways are stumbling blocks to its further development.^{14–17} The N₂ reduction reaction (NRR) to synthesize ammonia also faced the N₂ activation problem. In addition, the diversity of by-product type (*i.e.* H₂, N₂H₄, NO₂[−], etc.) in NRR or NO₃RR (NO₃[−] reduction reaction) limits the ammonia synthesis efficiency as well.^{18–21} The catalyst is the key to the catalytic reaction, where an excellent catalyst can effectively improve catalytic activity, selectivity, and stability by enhancing the adsorption and activation of the reactant, regulating the adsorption ability of the intermediate, reducing the limiting-rate-step barrier, promoting mass transfer, etc.^{22–24}

Department of Materials Science and Engineering, Centre for Atomic Engineering of Advanced Materials, Key Laboratory of Structure and Functional Regulation of Hybrid Materials of Ministry of Education, Key Laboratory of Functional Inorganic Material Chemistry of Anhui Province, Anhui University, Hefei 230601, China. E-mail: duyuanxin@ahu.edu.cn; zmz@ahu.edu.cn



Therefore, accelerating the development of novel highly-efficient catalysts *via* rational design and precise construction is of great significance.

In order to improve the reactivity per unit volume of the catalyst, there are two main strategies: one is to increase the number of active sites and the other is to improve the reaction rate. Catalyst miniaturization is an effective method to realize the former strategy.^{25–29} In recent years, with progress in nano-material preparation methods and the rapid development of fine structure characterization techniques, scientists have been able to achieve the controllable preparation of nanoparticles (NPs), from tens of nanometers to precise nanoclusters (NCs) composed of a few to several hundred atoms, and then to single atom catalysts (SACs), maximizing the utilization rate of atoms and achieving atomic economy.^{30–32} The latter is strongly influenced by the adsorption, activation and desorption behaviours of reactants, intermediates and products on the catalyst surface. By using atom doping to exert a synergistic effect between the components, these behaviours can be regulated and optimized to obtain an appropriate and matchable interaction between the reaction molecules and the catalyst, and then realizing an improvement in the catalytic reaction rate.^{33–35} Metal NCs, as an emerging type of nanocatalyst, bridging the gap between metal NPs and SACs, has attracted extensive interest due to the characteristic of having a unique molecule-like discrete electronic energy different from those of metal NPs or SACs.^{36–39} In addition, compared to its large counterpart metal NPs, metal NCs have relatively small size with higher atomic utilization and abundant surface unsaturated coordination active sites.^{40–42} In comparison to SACs, metal NCs exhibit the possibility of a synergistic effect.^{43,44} Furthermore, metal NCs show great adjustability in terms of catalytic properties, because at the sub-nanometer scale, even a single atom change will have a huge impact on the properties of the material.^{45–47}

In recent years, research on metal NC catalysis has undergone explosive growth, especially, those metal NCs with precise composition and structure, due to the potential opportunity to investigate the catalytic mechanism based on a clear structure–activity relationship.^{32,40,48,49} Au has for a long time been considered an unreactive noble metal. In the 1980s, Haruta and Hutching *et al.* discovered that small Au NPs exhibit extraordinary catalytic activity in CO oxidation and acetylene hydrochlorination, which has caused a boom in research into Au catalysis.^{50,51} Within the large family of precise NCs, atomically precise Au-based NCs show high stability and ready solubility in various solvents, which is very important for practical catalytic application.^{52,53} In addition, the advantages of easy preparation, high yield, and versatile surface functionalization are also the foundation of Au-based NCs as excellent catalysts.^{54–63} For example, the typical representative, Au₂₅ series NCs, can be seen as the standard-bearer of the NC family due to their early discovery (successfully synthesized in 1998 and structurally determined in 2008), and in-depth investigation (properties of optics, chirality, magnetism, electrochemistry, *etc.*), and wide application (catalysis, chemical sensing, imaging, bio-labeling, *etc.*).^{64,65} Furthermore, a variety of derivatives with abundant

diversity in terms of properties can be obtained by metal doping, changing ligands, regulating charge states, *etc.*^{64–66}

Among various adjustment strategies, heteroatom doping is an effective way to significantly expand the diversity of the composition and structure of NCs and provide a potential synergistic effect for improving catalytic performance. Speaking of a synergistic effect, it is a widely known concept among the public. Simply put, in the field of catalysis, a synergistic effect refers to the catalytic performance produced by the combination of multiple components surpassing that of a single component. It is mainly manifested through synergistic effects between metal atoms, between metals and supports, and between metal atoms and ligands. Here, we focus on the synergistic effects between metal atoms, reflected in the interactions between different metal active centers. Taking the ternary catalyst PtPdRh in automobile exhaust treatment as an example, Pt is mainly responsible for catalyzing the oxidation reaction of CO and CH_x, converting them into non-toxic CO₂ and H₂O. Pd also participates in this process, mainly playing a role in heat resistance and improving stability. Rh is mainly responsible for catalyzing the reduction reaction of NO_x, converting them into N₂ and O₂. The synergistic effect among the three achieves efficient catalytic activity and stability.

More importantly, the selective and purposeful introduction of foreign atoms into a monometallic NC can rationally optimize catalytic performance *via* modulation of electronic structure, additional active sites, and improvement in structural stability.^{43,67,68} Many researches have reported that Au NCs can be partially substituted with Ag, Cu, Pt, Pd, Cd, Hg, or Ir, and the Au-based alloy NCs perform with superior catalytic activity to their parent Au NCs in numerous reactions due to the synergistic effect.⁶⁹ Motivated by the current era of rapid development of NC materials and energy catalysis, herein, recent advances in atomically precise Au-based bimetallic NCs in energy-related small-molecule catalytic conversion are reviewed, including a summary of common synthesis strategies and structural characteristic of Au-based bimetallic NCs, and a discussion of the synergistic effect on catalytic activity, selectivity, and stability in HER, OER, ORR, CO₂RR, NRR, NO₃RR, *etc.*

2. Synthesis strategy and structural characteristic of Au-based bimetallic NCs

This section briefly introduces the general synthetic method for Au-based bimetallic NCs and their structural characteristics, such as heteroatom doping number, type and position. The precise and controllable synthesis of materials with high purity and yield is the basis for a benign industrial catalyst. However, synthesizing clusters with precise structures is not an easy task. After extensive attempts and efforts by researchers, it was not until Zhu *et al.* determined the crystal structure of Au₂₅(SR)₁₈ clusters using X-ray single crystal diffraction in 2008 that the synthesis of atomically precise metal clusters entered a stage of explosive growth.⁷⁰ Our previous review summarized several synthesis strategies for atomically precise metal NCs, such as



the direct synthesis method, size-focusing method, ligand-exchange method, chemical etching method, reduction method, metal-exchange method, separation method, inter-cluster reaction method, and anion-template-assisted method.⁴⁸ In addition, a lot of cluster-related reviews have summarized synthesis methods.^{36–39,71} Besides those mentioned above, others such as mass-selected gas-phase method, template methods, photoreduction method, sonochemical method, microemulsion method, radiolytic method, electrochemical method, and the microwave-assisted method, have also been successfully applied in cluster synthesis. However, not all methods are suitable for the synthesis of bimetallic NCs. Here, we mainly introduce synthesis methods applicable to bimetallic clusters, where common and general methods include the direct co-reduction strategy, cation-assisted strategy, anti-galvanic reduction (AGR) strategy, metal-exchange strategy, and intercluster reaction strategy. The basic principles of these methods are refined and summarized, and corresponding application examples are provided for readers to understand.

Direct co-reduction strategy: It usually takes a metal–ligand complex (*i.e.* Au–SR, Ag–SR, *etc.*) as a precursor and directly synthesizes bimetallic NCs with a reducing agent (*i.e.* NaBH₄, CO, *etc.*); it is also called “*in situ*” or “one-pot” synthesis.^{48,69} For example, Au_{25–x}Ag_x(SR)₁₈ NCs with continuously modulated *x* have been successfully synthesized by this method.⁷²

Cation-assisted strategy: this refers to the synthesis of bimetallic NCs by the reaction of the existing parent NCs with another metal cation.⁶⁹ For instance, Murray *et al.* obtained Au_{25–x}Ag_x(SR)₁₈ NCs by utilizing Ag⁺ ions reacting with Au₂₅(SR)₁₈ NCs.⁷³

Anti-galvanic reduction (AGR) strategy: Wu *et al.* proposed that the redox potential of the order of metals is no longer the only decisive thermodynamic parameter when the size of NCs is less than 3 nm.⁷⁴ They prepared Au–Ag and Au–Cu bimetallic NCs by doping heteroatoms in Au₂₅(SR)₁₈ on the basis of the AGR method.^{75,76}

Metal-exchange strategy: instead of using an inorganic metal salt, an organic metal–ligand complex is used in the synthesis of bimetallic NCs, and this synthesis process can no longer relate to the rule of metal redox potential.⁷⁷ For example, our group utilized Au₂₅(SR)₁₈ as a template to synthesize Cd₁Au₂₄(SR)₁₈ and Hg₁Au₂₄(SR)₁₈ by this method.⁷⁸

Intercluster reaction strategy: this refers to the preparation of new bimetallic NCs *via* the reaction between two stable NCs.^{48,69} For example, (Au_{25–x}Ag_x)(SR)₁₈ and Au_xAg_{44–x}(SR)₃₀ NCs are obtained by spontaneously exchanging metal atoms after mixing Au₂₅(SR)₁₈ and Ag₄₄(SR)₃₀.⁷⁹

For bimetallic NCs formed by heteroatom doping, the most important considerations are the type, number and position of the doping atoms, because these structural parameters have a great influence on the catalytic performance. Considering that NCs can be viewed as being composed of a metal kernel and a metal–ligand motif, the doping position of the heteroatom can be divided into center doping, kernel doping, kernel surface doping, and motif doping (Fig. 1). For motif doping, the heteroatom is connected with the coordination atom of the

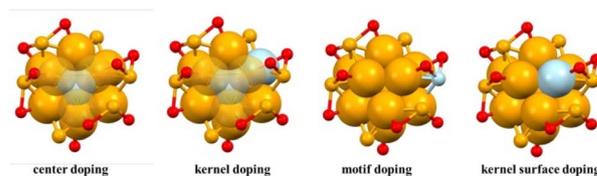


Fig. 1 Schematic diagram of the doping position of the heteroatom in Au-based bimetallic NCs. Atom colors: Au = orange, heteroatom = blue, S = red.

ligand, such as S, P, or N atoms. It is located on the outside of the cluster and has the opportunity to make direct contact with the reactant. For kernel doping (including center doping and kernel surface doping simultaneously) and kernel surface doping, the heteroatom is located at the surface of the metal core. When the catalytic reaction occurs, some ligands will detach due to the weak connection between metal atoms and ligands, and the atoms at the surface of the metal core are exposed as active centers to directly participate in the reaction. For center doping, the heteroatom is located at the center of the metal core, and it seems to have no influence on catalysis due to the indirect contact with the reactant. However, it can participate in the catalytic reaction by modulating the electronic structure of the metal core, regulating the interaction strength with the reactant or intermediate, and optimizing the reaction pathway and kinetics. The synthesis methods and characteristic structural parameters of Au-based bimetallic NCs reported in recent years are summarized in Appendix Table 1.

3. Au-based bimetallic NCs in energy-related catalysis

Aiming at current attractive energy-related catalytic reactions, this part classifies, summarizes, and discusses recent progress in the synergistic effects of Au-based bimetallic NCs in the hydrogen evolution reaction, oxygen evolution reaction, oxygen reduction reaction, fuel small-molecule oxidation reaction, carbon dioxide reduction reaction, and synthetic ammonia reaction.

3.1 Au-based bimetallic NCs in the hydrogen evolution reaction

The gradual depletion of fossil fuels and consequent environmental and climate concerns have stimulated the development and use of clean and renewable energy sources. Among various clean energy carriers, hydrogen with its high energy density is considered to be one of the promising energy resources for a sustainable society.⁸⁰ The hydrogen evolution reaction (HER), which uses the abundant water on Earth as a raw material and is driven by renewable energy, such as hydropower, photovoltaic, wind, or tidal energy, is an ideal method of hydrogen production, which has many advantages, including environmental friendliness, production of high-purity hydrogen, and low carbon emissions.⁸¹ Currently, the mainstream prediction method for the superiority of the HER catalyst is based on the



volcano plot, which is constructed by linking the hydrogen adsorption energy with the exchange current.⁸² According to the Sabatier principle, a good HER catalyst does not bind the hydrogen too weakly or too strongly; therefore, a nearly thermodynamically neutral hydrogen binding step is assurance of a good HER catalyst.⁸³

At present, Pt is recognized as the best-known efficient HER electrocatalyst; however, its high cost and scarce stocks hamper its large-scale industrial application.⁸⁴ As the sixth period element in the periodic table next to Pt, the electronic structure of Au is similar to that of Pt, so there is reason to believe that Au NCs have the potential to be an outstanding HER catalyst.^{85,86} Kwak *et al.* selectively replaced the center Au atom in Au₂₅ NCs with a single Pt atom and obtained Pt₁Au₂₄ bimetallic NCs (Fig. 2a).⁸⁷ Pt doping has little effect on the geometric structure of the NCs; Pt₁Au₂₄ almost maintains the configuration of the original Au₂₅. However, the electronic structure changes a lot, which is reflected in the surface charge state ([Pt₁Au₂₄]⁰ & [Au₂₅]⁻), superatomic electronic configuration (Au₂₅: 8-electron, Pt₁Au₂₄: 6-electron)^{88–90} and optical absorbance spectra (Au₂₅: 1.8 eV, Pt₁Au₂₄: 1.1 and 2.1 eV). The redox behavior is also drastically altered. As measured by square-wave voltammetry (SWV), the gaps between the first oxidation (O1) and reduction (R1) potential for Au₂₅ and Pt₁Au₂₄ are 1.67 and 0.73 V, respectively (Fig. 2b). The HOMO–LUMO (highest occupied–lowest unoccupied molecular orbitals) gaps are 1.32 and 0.29 eV for Au₂₅ and Pt₁Au₂₄, respectively. It is worth noting that the reduction potential of Pt₁Au₂₄ is nearly 1 V more positive than that of Au₂₅, indicating the possibility of a lower overpotential for the electrocatalytic reduction reaction. This conjecture is further confirmed by the result of linear sweep voltammograms (LSVs). In THF (0.1 M Bu₄NPF₆) solution containing 1.0 M trifluoroacetic acid (TFA), Au₂₅ and Pt₁Au₂₄ show onset potentials at –1.10 and –0.89 V, respectively (Fig. 2c).

Notably, the overpotential for Pt₁Au₂₄ is ~70 mV (relative to –0.82 V, the thermodynamic reduction potential of a proton in THF with 1.0 M TFA), which is superior to other natural hydrogenase enzymes (~100 mV).^{91–93} With an increase in TFA concentration, the current at –0.76 V (the first reduction [Pt₁Au₂₄]^{0/–}) of Pt₁Au₂₄ shows no significant change, while the current at –1.10 V (the second reduction [Pt₁Au₂₄]^{–/2–}) is significantly enhanced, suggesting that Pt₁Au₂₄ acts as an electron transfer mediator for HER (Fig. 2d).^{94,95} The *k*_{obs} (pseudo-first-order rate constant) of Pt₁Au₂₄ is calculated to be 121000 s^{–1} at η = 650 mV, which is higher than that of Au₂₅ (8000 s^{–1}) or other molecule-like complexes (Co-complex: 700 s^{–1} at η = 890 mV, Cu-complex: 11000 s^{–1} at η = 720 mV, Ni-complex: 106000 s^{–1} at η = 650 mV) (Fig. 2e).^{96–98}

In addition, Pt₁Au₂₄ shows charge-state-dependent catalytic activity, indicating molecule-like catalytic behavior different from that of the larger-sized metal NPs. The currents at potentials negative to the [Pt₁Au₂₄]^{–/2–} all exhibit linear correlation with [Pt₁Au₂₄] and [TFA]^{1/2}, suggesting a heterolytic HER mechanism, [H–Pt₁Au₂₄][–] + H⁺ → [Pt₁Au₂₄]⁰ + H₂. In contrast, the current at the potential at which [Pt₁Au₂₄][–] exists as the predominant form shows linear correlation with [TFA] and [Pt₁Au₂₄]^{3/2}, indicating a homolytic HER mechanism, [H–Pt₁Au₂₄]⁰ + [H–Pt₁Au₂₄]⁰ → 2[Pt₁Au₂₄]⁰ + H₂. The heterolytic HER mechanism over Pt₁Au₂₄ is further confirmed by density functional theory (DFT) calculations with an energy change of –0.155 eV, while for Au₂₅, the thermodynamically favorable HER pathway is the homolytic mechanism (Fig. 2f). Additionally, an H–Pt bond can spontaneously form. The bond length between adsorbed H and central Pt is shorter than that between adsorbed H and surface Au, indicating that the stronger H–Pt interaction is beneficial for HER energetics on [Pt₁Au₂₄]^{2–}. As a result, Pt₁Au₂₄ exhibits excellent HER activity whether for homogeneous catalysis in non-aqueous solvent or

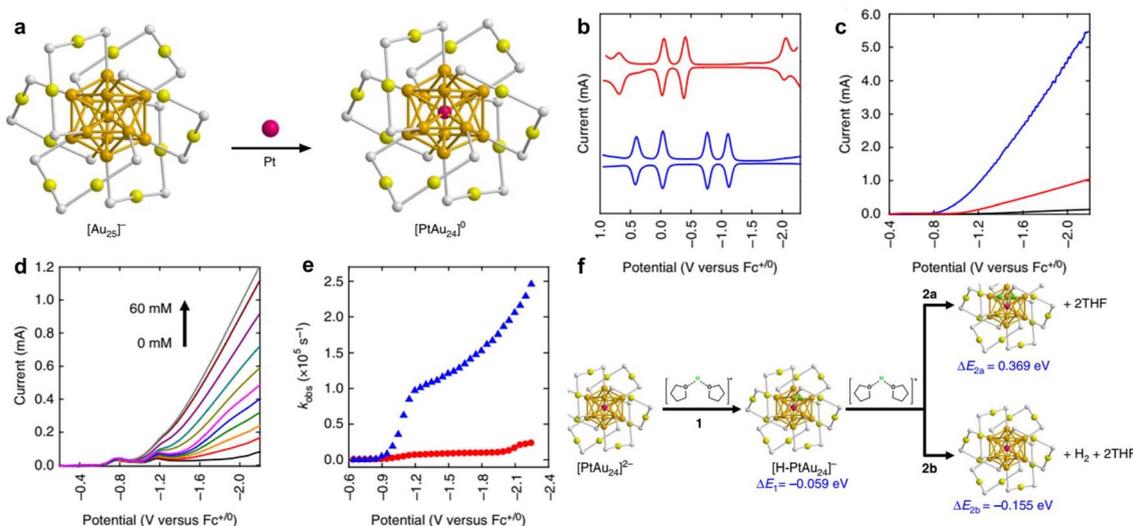


Fig. 2 (a) Structure of Au₂₅ and Pt₁Au₂₄ NC. (b) SWVs of Au₂₅ (red) and Pt₁Au₂₄ (blue) in CH₂Cl₂ (0.1 M Bu₄NPF₆). (c) LSVs in THF (0.1 M Bu₄NPF₆) solution containing 1.0 M TFA without a catalyst (black) and with Au₂₅ (red) and Pt₁Au₂₄ (blue). (d) LSVs of Pt₁Au₂₄ in THF (0.1 M Bu₄NPF₆) with different concentrations of TFA. (e) *K*_{obs}–potential plots for Au₂₅ (red) and Pt₁Au₂₄ (blue). (f) Reaction energy calculation for HER on Pt₁Au₂₄. Reproduced from ref. 87 with permission from Springer Nature, copyright 2017.

heterogeneous catalysis in aqueous media, compared to Au₂₅, other molecule-like complexes, or commercial Pt/C benchmarking.

Recently, Sun *et al.* revisited the electrocatalytic HER activity origin of Pt₁Au₂₄ NCs by a combination of advanced first-principles calculations and attenuated total reflection surface-enhanced infrared absorption spectroscopy (ATR-SEIRAS) experiments.⁹⁹ They found that in addition to the central Pt atom, the exposed bridged Au site, due to spontaneous thiolate ligand desorption during the electrochemical process, is also a catalytically active site. The synergistic effect between the two types of active site contributes to the extraordinary HER activity of the Pt₁Au₂₄ cluster. As Pt centrally doped Pt₁Au₂₄ significantly improves HER activity, it is natural for researchers to ask whether Pd₁Au₂₄, which has a nearly isoelectronic structure and similar redox property, would also exhibit similarly high HER activity. Choi *et al.* systematically compared the HER catalytic activity parameters, such as onset potential (E_{onset}), current density, and turnover frequency (TOF) of M₁Au₂₄ and M₂Au₃₆ (M = Pt, Pd).¹⁰⁰ Compared to non-doped Au NCs, atom doping not only brings about a change in the electrochemical redox property, but also causes an improvement in HER activity. E_{onset} is determined by the match between the reduction potential of NC and H⁺. In both M₁Au₂₄ and M₂Au₃₆ systems, Pt doping shows higher current density and TOF than Pd doping, which is attributed to the lower H adsorption free energy (ΔG_{H}) in Pt-doped Au NCs (Fig. 3a). Based on the excellent HER performance of Pt₁Au₂₄, Negishi *et al.* further changed the surface ligand to, for example, C6 = 1-hexanethiolates, TBBT = 4-*tert*-butylbenzenethiolate, PDT = 1,3-propanedithiolate, or PET = 2-

phenylethanethiolate, in pursuit of higher catalytic activity.¹⁰¹ Due to the differences in the lengths and orientations of -Au(I)-SR-Au(I)- staples between TDT/PDT- and C6/PET-protected NCs, the Au atoms of the Pt₁Au₁₂ metal core in TDT/PDT-protected Pt₁Au₂₄ NCs are exposed on the outside, resulting in enhanced HER activity. Although Ag is considered to be inactive for HER, obtaining AuAg alloy NCs with comparable HER activity is highly possible *via* a reasonable design. Li *et al.* synthesized Au₃₆Ag₂(SR)₁₈ NCs, which can be regarded as having a trimeric structure, that is with three icosahedral (I_{h}) units face-fused together in a cyclic manner.¹⁰² The unique face-fusion mode in Au₃₆Ag₂ endows it with unfilled superatomic orbitals, a low ligand-to-metal ratio, and low-coordinated Au atoms, leading to lower ΔG_{H} and higher electron affinity, thus showing improved HER activity over its counterpart monomeric Au₂₅ and dimeric Au₃₈ (Fig. 3b and c).

In addition to the synergies between different metal components within clusters, there are also interactions between NCs and functional carriers, which can be combined in one system to maximize synergies. Du *et al.* designed and synthesized Au₂Pd₆ NCs, which can be considered to be two Pd₃ NCs connected by an Au₂ unit.¹⁰³ On the one hand, after MoS₂ couple metal NCs, the number of catalytic active sites is increased, and electron transport is promoted, resulting in enhanced HER activity. On the other hand, compared to monometallic Au₂ and Pd₃ NCs, and mixed Au₂-Pd₃ NCs, bimetallic Au₂Pd₆ shows the best HER activity with the lowest overpotential, the smallest Tafel slope and electrochemical resistance, and the largest electrochemically active surface area and TOF value (Fig. 3d-i). X-ray photoelectron spectroscopy and Raman results indicate

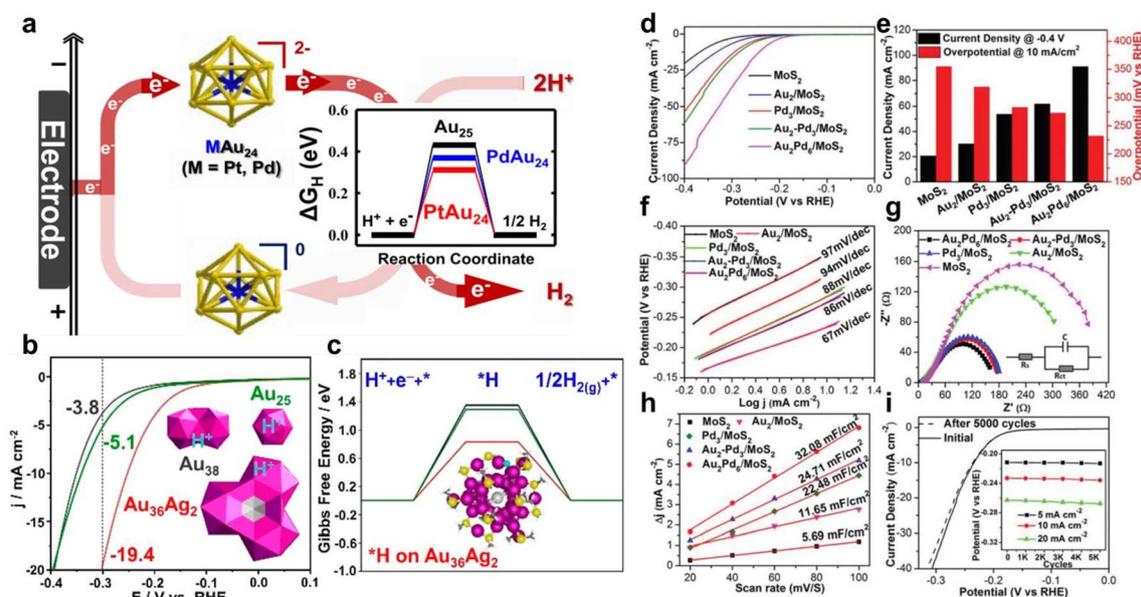


Fig. 3 (a) Schematic diagram of M₁Au₂₄ (M = Pt, Pd) enhanced HER activity compared to Au₂₅ NCs. Reproduced from ref. 100 with permission from American Chemical Society, copyright 2018. (b) LSVs and (c) ΔG_{H} of Au₂₅, Au₃₈, and Au₃₆Ag₂. Reproduced from ref. 102 with permission from American Chemical Society, copyright 2021. (d) LSVs, (e) current density and overpotential comparison, (f) Tafel slope, (g) electrochemical impedance spectroscopy, and (h) electrochemical double-layer capacitance of MoS₂, Au₂/MoS₂, Pd₃/MoS₂, Au₂-Pd₃/MoS₂, and Au₂Pd₆/MoS₂. (i) Stability test of Au₂Pd₆/MoS₂. Reproduced from ref. 103 with permission from Royal Society of Chemistry, copyright 2018.



the strong electronic interaction between NCs and MoS₂. DFT calculations demonstrate that the largest number of catalytic sites with almost nearly zero ΔG_{H} occur on Au₂Pd₆/MoS₂, further explaining the excellent HER activity of Au₂Pd₆/MoS₂ from a theoretical perspective. A similar phenomenon is observed on bimetallic Au₄Cu₂ NCs, which show better HER activity than that of monometallic Cu₆ or Au₆ NCs.¹⁰⁴ Taking atomically precise alloy NCs as a precursor to proceed with ligand-assisted pyrolysis is a novel method to form nanocluster/single atom (NC/SA) composite systems. Lv *et al.* obtained a hybrid system containing two different active sites types, AuPd alloy NCs and satellite Pd SAs (AuPd_{NCs}/Pd_{SAs}), by controllable thermal treatment of Au₄Pd₂(SC₂H₄Ph)₈.¹⁰⁵ In the hybrid system, the satellite Pd SAs play the role of optimizing the electronic structure, and the Au sites effectively promote the adsorption and dissociation of H₂O molecules. Thereby, the synergy between Au and Pd promotes the excellent HER activity of AuPd_{NCs}/Pd_{SAs}-600, which shows one order of magnitude higher mass activity and TOF than commercial Pd/C or Pt/C.

In addition to electrocatalytic HER, solar-driven photocatalytic water splitting is a sustainable and clean approach to produce hydrogen. Metal NCs exhibit a molecule-like discrete electronic energy band and strong light absorption in broad spectra, which meet the basic requirements for potential promising photocatalysts.¹⁰⁶ Bootharaju *et al.* synthesized a selenolated [Au₁₂Ag₃₂(SePh)₃₀]⁴⁻ core-shell cluster based on a templated galvanic exchange strategy, which is comprised of an Au icosahedral core and an Ag₁₂(SePh)₃₀ shell.¹⁰⁷ The synergistic effect between the Au core and the Ag shell greatly changes the overall electronic structure, which aligns well with the band structure of TiO₂, facilitating photogenerated charge carrier separation. Therefore, Au₁₂Ag₃₂/TiO₂ shows a photocatalytic H₂ production rate of 6810 $\mu\text{mol g}^{-1} \text{h}^{-1}$ under solar irradiation, which is 37.8 and 6 times higher than those of TiO₂ and Ag₄₄/TiO₂, respectively (Fig. 4a and b). Liu *et al.* obtained [Au_xAg_{25-x}(SR)₁₈]⁻ series NCs (1 ≤ x ≤ 3, 3 ≤ x ≤ 8, 19 ≤ x ≤ 23, defined as NC-1, NC-2, NC-3).¹⁰⁸ Under visible-light irradiation, the H₂ production rate follows the order: NC-3 > NC-2 > NC-1 > Au₂₅ > Ag₂₅. As revealed by DFT calculation, bimetallic Au_x-Ag_{25-x} shows that the better photocatalytic HER activity is due to the optimization of electronic structure caused by the Au-Ag synergy. The narrowed HOMO-LUMO gap in Au_xAg_{25-x} partially contributes to the better HER performance. What is more, the microenvironment localized in dual Au-Ag sites benefits the formation of electron-acceptor centers, resulting in photo-generated electrons tending to remain in a cluster to reduce the adsorbed H⁺ (Fig. 4c). Additionally, the Au-Ag bimetallic synergistic effect upshifts the D-band centers and balances hydrogen adsorption/desorption dynamics (Fig. 4d and e). Kurashige *et al.* loaded Pd₁Au₂₄ and Pt₁Au₂₄ on BaLa₄Ti₄O₁₅ *via* stepwise ligand-exchange, adsorption, and calcination processes, to investigate the effect of heteroatom doping type on photocatalytic HER activity.¹⁰⁹ Although the Pd and Pt atoms are both in the center of M₁Au₂₄ when it exists in the form of NCs alone, the positions of Pd and Pt atom are different after depositing them on BaLa₄Ti₄O₁₅. As can be rationally inferred from extended X-ray absorption fine structure (EXAFS)

spectroscopy results, Pd is located at the surface of the NCs, while Pt is at the interface between NCs and BaLa₄Ti₄O₁₅. Whether Pd or Pt doping is used, the electron density of Au in the NCs is improved. However, for photocatalytic HER activity opposite results are obtained, where Pt doping increases the activity; in contrast, Pd doping causes a decrease in activity, which to a great degree can be attributed to the doping position of the heteroatom (Fig. 4f).

3.2 Au-based bimetallic NCs in the oxygen evolution reaction

The oxygen evolution reaction (OER) is an elementary reaction of great importance in the field of energy and the environment. It refers to the half-reaction that occurs on the anode during electrolysis of H₂O. Because OER involves a four-electron transfer process, it exhibits slow reaction kinetics, and requires higher energy to trigger a reaction; therefore, it is the key factor restricting the efficiency of an overall H₂O electrolysis device.^{110,111} Liu *et al.* synthesized an alkynyl-protected AuAg alloy cluster, Au₁₅Ag₂₃(^tBuC≡C)₁₈Br₆, which has a triple-layered core-shell-shell (Au₆@Au₆Ag₂₃@Au₃) configuration.¹¹² Au₁₅Ag₂₃ not only shows excellent electrocatalytic HER activity ($\eta = 125$ mV to reach 10 mA cm⁻² current density) but it also displays an outstanding OER property when it is loaded on NiFe layered double hydroxide, whose overpotential is 250 mV to reach 10 mA cm⁻² (Fig. 5a). In an overall water splitting (OWS) system, achieving 10 mA cm⁻² requires only 1.51 V, and it performs for as long as 50 h in a stability test.

The electrocatalytic OWS performance of Au NCs can be regulated by utilizing the electron-attracting ability of an Fe atom to Au NCs. Sun *et al.* synthesized a hybrid system of Au-Fe₁NCs loaded on Ni foam to act as alkaline HER and OER bifunctional electrocatalysts.¹¹³ The electron structure of H adsorption on the Au NC surface is optimized by the introduction of Fe atoms, manifested by a low overpotential of 35.6 mV to reach 10 mA cm⁻² current density in HER. In addition, the hybrid system Au-Fe₁NCs display good OER activity with a 246 mV low overpotential at 10 mA cm⁻² oxidation current density. In a two-electrode alkaline OWS device, the cell voltage to reach 10 mA cm⁻² current density is only 1.52 V, and the durability test lasts for 40 h. The synergistic effect in Au-Fe₁NCs is elucidated by X-ray photoelectron spectroscopy (XPS) experiments and DFT theoretical calculations, mainly reflected in the promotion of electron delocalization and enhancement of O-H bond activation of Au NCs and an upshift in the D-band center of the Fe atom.

The synergistic effect induced by heteroatom doping has shown great improvement in electrochemical activity; however, the understanding of the effect on photo-/photoelectro-catalytic activity, especially that involving charge transfer characteristics, remains blank. Su *et al.* took glutathione-protected Ag-doped Au NCs (Au_{1-x}Ag_x@GSH) and a non-conjugated insulating polymer of poly(diallyl-dimethylammonium chloride) (PDDA), as negatively and positively charged building blocks to elaborately fabricate a spatially multilayered alloy NCs/metal oxide photoanode heterostructure *via* layer-by-layer (LBL) assembly.¹¹⁴



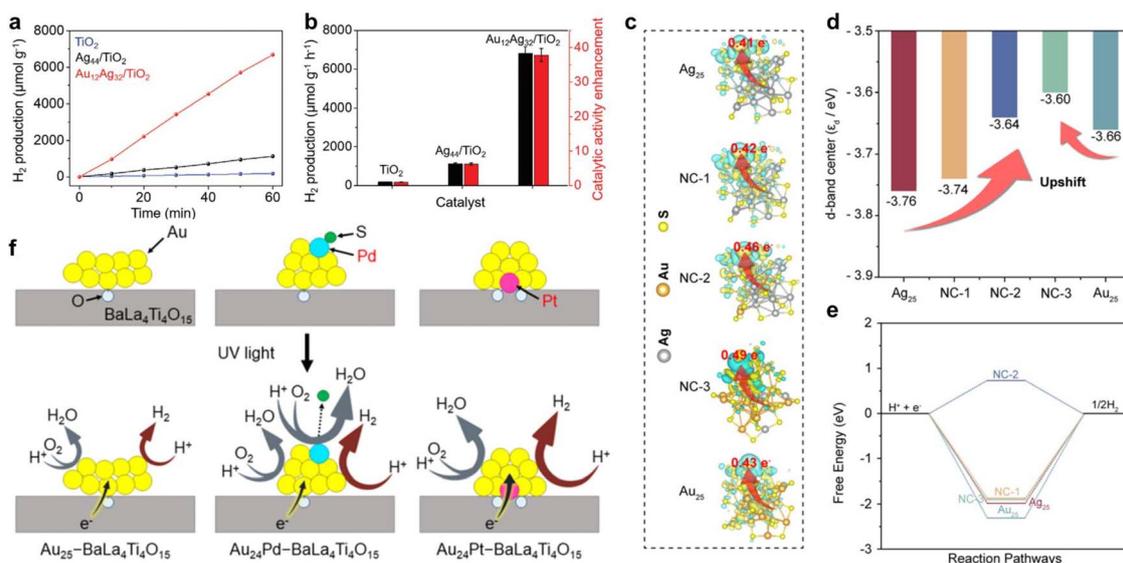


Fig. 4 (a and b) Comparison of photocatalytic HER activity of TiO₂, Ag₄₄/TiO₂, and Au₁₂Ag₃₂/TiO₂. Reproduced from ref. 107 with permission from Wiley-VCH, copyright 2023. (c) The isosurfaces of charge density difference of H⁺-adsorbed NCs. (d) D-band center and (e) ΔG_H of [Au_xAg_{25-x}(SR)₁₈]⁻ series NCs. Reproduced from ref. 108 with permission from Royal Society of Chemistry, copyright 2023. (f) Proposed structures of M₁Au₂₄-BaLa₄Ti₄O₁₅ for M = (Au, Pd, Pt) before (top) and during (bottom) the water splitting reaction. Reproduced from ref. 109 with permission from American Chemical Society, copyright 2019.

Au_{1-x}Ag_x@GSH acts as a photosensitizer that can be instantly photoexcited to generate e⁻ and h⁺, and PDDA plays the role of an electron-withdrawing mediator to accelerate interfacial charge transfer and form a cascade electron transport channel. As a result, LBL-assembled TiO₂/(PDDA-Au_{1-x}Ag_x)_n shows good photoelectrochemical H₂O oxidation performance under visible-light irradiation.

3.3 Au-based bimetallic NCs in the oxygen reduction reaction

The electrocatalytic oxygen reduction reaction (ORR) is the process by which oxygen is reduced to water or other oxygen-containing species in an electrochemical system. ORR usually has two reaction pathways, one of which is the 4-electron

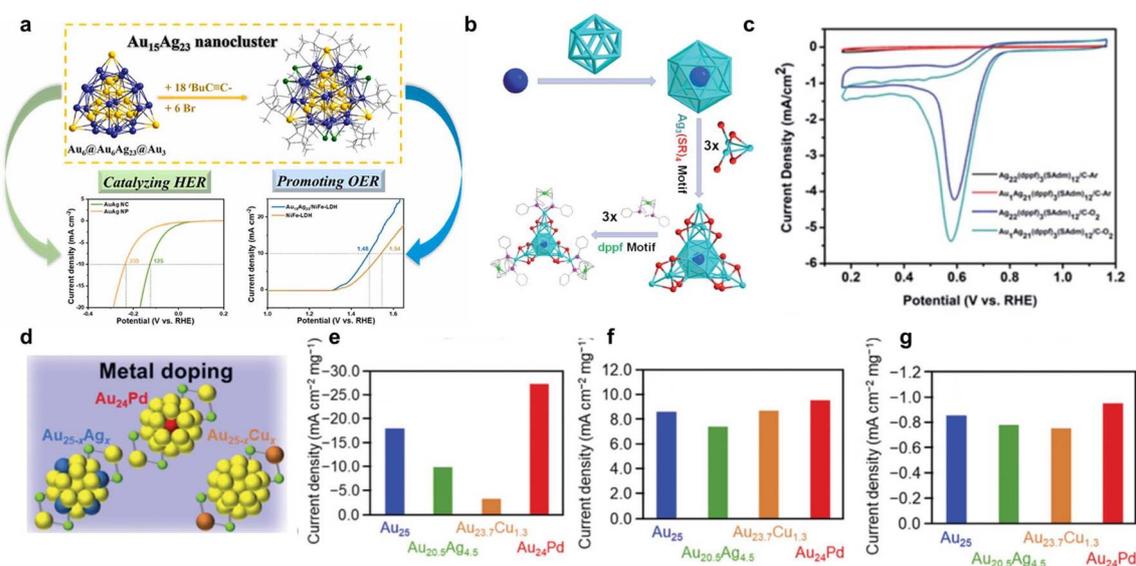


Fig. 5 (a) Schematic diagram of Au₁₅Ag₂₃ NC as efficient HER and OER catalyst. Reproduced from ref. 112 with permission from Elsevier, copyright 2024. (b) Structural analysis of Au₁Ag₂₁ NC. (c) Comparison of ORR performance of Au₁Ag₂₁ and Ag₂₂ NC. Reproduced from ref. 124 with permission from Royal Society of Chemistry, copyright 2021. (d) Structural scheme of metal-doped Au₂₅ NC. Comparison of (e) HER, (f) OER, and (g) ORR activity of Au₂₅ and different metal-doped Au₂₅ NCs. Reproduced from ref. 127 with permission from Royal Society of Chemistry, copyright 2020.



reduction process, starting from O_2 to H_2O , and it is one of the key reactions in energy conversion devices such as fuel cells and metal-air batteries, and its efficiency has a decisive impact on the performance of these devices.^{115,116} While the other one is the 2-electron pathway, converting O_2 to H_2O_2 , which can serve as a promising alternative to the traditional energy-intensive anthraquinone process.^{117–119}

According to theoretical calculation, the decrease in the core size of Au NPs will result in a narrowed D-band and shift to the Fermi level, which are considered to be beneficial for O_2 adsorption.^{120,121} At an early stage, Chen *et al.* utilized two series of Au NCs with different core sizes to investigate the effect of size on ORR activity, and they found the ORR catalytic activity of both follows the trend where a smaller size of NCs results in better ORR reactivity ($Au_{11} > Au_{25} > Au_{55} > Au_{140}$ and $Au_{25} > Au_{38} > Au_{144}$).^{122,123} Besides the core size of the NCs, heteroatom doping is another critical factor influencing the ORR activity of Au NCs. Zou *et al.* synthesized $M_1Ag_{21}(dppf)_3(SAdm)_{12}(BPh_4)_2$ ($M = Au/Ag$) by introducing 1,1'-bis-(diphenylphosphino)-ferrocene (dppf) as an activating ligand.¹²⁴ Dppf is a derivative of ferrocene as well as an electron donor, acting as a common protective ligand used to design and synthesize a metal complex with excellent electrochemical activity. Compared to other Au/Ag NCs without a dppf ligand, the two NCs show better ORR activity. In addition, the two NCs exhibit the same icosahedral M_{13} ($M = Au/Ag$) kernel with a protective shell of 3 $Ag_3(SR)_4$ motifs and the protection of 3 dppf ligands (Fig. 5b). The identical geometric structure provides an ideal platform to reveal the heteroatom doping effect. Au_1Ag_{21} shows higher onset potential and diffusion limited current density, indicating better ORR activity than that of Ag_{22} (Fig. 5c).

Xu *et al.* simultaneously introduced a dppf surface ligand and a Cd surface doping atom to perform a surface engineering strategy, and then obtained $Au_{27}Cd_1(SAdm)_{14}(dppf)Cl$ NCs.¹²⁵ $Au_{27}Cd_1$ and Au_{38} NCs have a similar bi-icosahedral Au_{23} core, but different surface structures due to surface engineering. The reconstructed surface structure offers enhanced ORR activity for $Au_{27}Cd_1$. The synergistic effect between Au and Cd is not only reflected in a comparison of the ORR catalytic activity of $Au_{27}Cd_1$ and Au_{38} NCs but is also manifested in the improved ORR activity of $Au_{22}Cd_1$ compared to that of Au_{24} NCs. Furthermore, based on the Koutecky–Levich plots, the overall number of electrons transferred for Cd-doped Au NCs is higher than that for bare Au NCs ($Au_{38} : 2$, $Au_{27}Cd_1 : 3.3$, $Au_{24} : 2.2$, $Au_{22}Cd_1 : 3$), indicating that Cd doping will change the ORR reaction pathway of Au NCs. In addition to Ag/Cd doping, AuPd alloy NCs show better ORR activity than Au NCs. Yan *et al.* synthesized GSH-protected AuPd NCs and tuned the structure and composition with the Pd-to-Au ratio.¹²⁶ The AuPd NCs are supported on carbon nanosheets and the protective ligand is completely removed by calcination. The hybrid composite with 30% metal mass loading and Pd-to-Au ratio of 1 : 2 exhibits optimized ORR activity.

Although there is lots of research into $Au_n(SR)_m$ -related alloy NCs in electrocatalytic HER, OER, and ORR, the activities are obtained under different experimental conditions, so it is difficult to make a deep comparison and develop a general rule

about the methods needed to achieve high activity. Kumar *et al.* systematically investigated the effect of heteroatom species on the activity of these reactions.¹²⁷ Compared to Cu/Ag doping, Pd-doped Au NCs show the highest current density in all three reactions (Fig. 5d–g). Other parameters, such as the number of constituent atoms or ligand functional groups, are also carefully evaluated. The results indicate that the decreased number of constituent atoms and thickness of the ligand layer are helpful for an improvement in activity in all three reactions.

3.4 Au-based bimetallic NCs in the fuel small-molecule oxidation reaction

A fuel cell is a chemical device that converts the chemical energy of a fuel directly into electrical energy. Theoretically, it can operate at close to 100% thermal efficiency. It exhibits lots of advantages, such as high economy, low environmental pollution, high reliability, a wide selection of fuels and easy construction.^{128–132} Depending on the type of fuel entering at the anode, different types of fuel cells can be obtained. For example, a direct ethanol fuel cell (DEFC) is a device that uses ethanol with its merits of high energy density, low cost and easy storage as a fuel to perform an anodic oxidation reaction and convert it into electric energy.^{133–135} Au NCs exhibit excellent performance in the ethanol oxidation reaction (EOR). Tang *et al.* reported alkynyl-protected $Au_{28}(DMPA)_{20}$ NCs ($DMPA = 1$ -ethynyl-2,4-dimethylbenzene) synthesized by a direct reduction method.¹³⁶ Compared to thiol-ligand-protected $Au_{28}(SR)_{20}$ (here $SR = TBBT/CPT$, $TBBT = 4$ -tertbutylbenzenethiol, $CPT =$ cyclopentanethiol) with a similar structure, $Au_{28}(DMPA)_{20}$ shows superior EOR mass activity and specific activity. In order to further improve the EOR activity, commercial Pd and Pt are introduced into Au NCs as heteroatom dopants. Zhang *et al.* synthesized surface-clean Pt_3Au NCs with a uniform size of 2.1 nm supported on PDDA-functionalized graphene ($Pt_3Au@PDDA-G$) by a CO reduction method.¹³⁷ The obtained Pt_3Au NCs not only effectively suppress Ostwald ripening but also show enhanced EOR activity due to the more efficient removal of the adsorbed CO-like intermediates based on the synergistic effect between Pt and Au. Similarly, Cui *et al.* utilized a wet-chemical method to synthesize AuPd NCs with an average size of 1.0 nm supported on amine-functionalized carbon black ($AuPd/CB_{H-A}$).¹³⁸ In EOR, $Au_{0.4}Pd_{0.6}/CB_{H-A}$ exhibits 5.25 $A\text{ mg}_{AuPd}^{-1}$ mass activity and 5.98 mA cm_{AuPd}^{-2} specific activity, which are 9.7 and 3.4 times greater than those of commercial Pd/C (0.54 $A\text{ mg}_{Pd}^{-1}$ and 1.74 mA cm_{Pd}^{-2}), respectively.

In addition, direct formic acid fuel cells (DFAFCs) fueled by formic acid are considered to be one of the most promising power sources for portable electronic devices in the future due to their small size, low toxicity and low penetration of Nafion membranes.^{139,140} Pt is generally considered to be the most effective catalyst towards the anodic reaction of DFAFCs, formic acid oxidation (FAO). However, due to its poor resistance to CO toxicity, its current development faces a bottleneck. Lu *et al.* synthesized single-Pt-atom-doped Au_{25} ($Pt_1Au_{24}(SR)_{18}$) NCs.¹⁴¹ Although only one Pt replaces the central Au atom, Pt_1Au_{24} shows excellent FAO performance with a high mass activity of



3.7 A $\text{mg}_{\text{Pt+Au}}^{-1}$, which is 12 and 34 times higher than that of Pt NCs and commercial Pt/C, respectively. Moreover, the unavailability of adjacent Pt atoms in $\text{Pt}_1\text{Au}_{24}$ NCs effectively suppresses the poisoning of CO intermediates, which is reflected in the outstanding performance in an accelerated durability test and CO stripping experiment. On the basis of *in situ* electrochemical FTIR observation and thermodynamic and kinetic calculation, the FAO process on $\text{Pt}_1\text{Au}_{24}$ is speculated to be a direct pathway with COOH^* as the preferred reactive intermediate. The introduction of a Pt atom leads to a decreased HOMO–LUMO gap and higher reactivity, and the original Au atomic shell plays a CO anti-poisoning role. The synergistic effect in $\text{Pt}_1\text{Au}_{24}$ NCs contributes to the high activity and good stability.

3.5 Au-based bimetallic NCs in the carbon dioxide reduction reaction

The catalytic conversion of carbon dioxide is the process of converting CO_2 into chemicals, energy products and functional materials to achieve resource utilization, which has great significance and application prospects for sustainable development. The use of low-grade renewable electricity to reduce CO_2 , which can both reduce CO_2 emissions and “turn waste into good”, and convert renewable energy into high energy density fuel storage, is considered a green and promising technique due to its flexible and sustainable method of conversion.^{142–146}

At present, the possible main products of CO_2 electro-reduction include C_1 products (e.g., carbon monoxide, formic acid, methane, methanol) and C_{2+} chemicals (e.g., ethylene, ethanol, ethane, *n*-propanol).¹⁴⁵ Among the different products of CO_2RR , the conversion of CO_2 to CO is considered to be one of the most promising reactions in the chemical industry due to its technical and economic feasibility.¹⁴⁷ Due to the relatively weak binding of $^*\text{CO}$ intermediates to Au, Au-based materials show particularly high selectivity for the formation of CO. It is believed that alloying or doping can further improve the CO_2RR efficiency of Au NCs by optimizing the electronic structure and surface geometry. Zhuang *et al.* employed $\text{Au}_{44}(\text{TBBT})_{28}$ as the parent NCs and chose Cd^{2+} as the oxidative ions to prepare $\text{Au}_{47}\text{Cd}_2(\text{TBBT})_{31}$ NCs by the anti-galvanic reduction (AGR) method in a two-phase system.¹⁴⁸ The doped Cd atoms are on the surface and are coordinated by three thiolates. Compared to $\text{Au}_{44}(\text{TBBT})_{28}$, $\text{Au}_{47}\text{Cd}_2(\text{TBBT})_{31}$ shows higher faradaic efficiency (FE) for CO over a wide potential range from -0.3 V to -0.9 V, displaying FE_{CO} up to 96% at -0.57 V (Fig. 6a). DFT calculations indicate that introducing Cd atoms results in a change in the adsorption configuration for the COOH^* intermediate. Unlike $\text{Au}_{44}(\text{TBBT})_{28}$, the O atom of COOH^* prefers to bind with Cd, leading to the formation of Cd-O-C(OH)-Au and decreased COOH^* formation energy, benefiting the enhancement in CO_2RR activity.

In addition, Li *et al.* synthesized Cd-surface-modified Au NCs ($\text{Au}_{19}\text{Cd}_2(\text{SR})_{16}$, $\text{SR} = \text{cyclohexanethiolate}$) by taking $\text{Au}_{23}(\text{SR})_{16}$ as the template.¹⁴⁹ Compared to Au_{23} , the kernel of $\text{Au}_{19}\text{Cd}_2$ is maintained, except that two surface Au atoms are replaced by Cd dopants. The introduction of Cd obviously improves the

selectivity and activity of CO formation. The determination of active sites is investigated in detail. Compared to the inactivity of fully ligand-protected NCs, partial ligand detachment is considered a necessity for high catalytic activity. However, it needs to be carefully studied which part ($-\text{R}$ or $-\text{SR}$) it is reasonable to remove, and which exposure site (S or Au) is the real catalytic site. Through DFT calculations, for both NCs, removing the $-\text{R}$ group is considered to be more feasible than losing the $-\text{SR}$ group, and the exposed S site is likely to be the active center for CO_2RR . In contrast, if $-\text{SR}$ is removed, the exposed Au site is more selective for HER than for CO_2RR . Furthermore, for $\text{Au}_{19}\text{Cd}_2$ NCs, the S active site (Cd-S-Au staple motif) will undergo a dynamic regeneration process during CO formation and desorption, contributing to the different $^*\text{CO}$ binding mode and leading to the decreased energy for CO formation (Fig. 6b). At the same time, Sun *et al.* investigated the CO_2RR activities of $\text{Au}_{25}(\text{SR})_{18}$, $\text{Au}_{24}\text{Cd}_1(\text{SR})_{18}$, $\text{Au}_{19}\text{Cd}_4(\text{SR})_{18}$, and $\text{Au}_{38}\text{Cd}_4(\text{SR})_{30}$, and found that Cd doping can selectively control the cleavage of the Au–S or C–S bond.¹⁵⁰ They reached a similar conclusion: that is, the exposed open S site obtained by cleaving the C–S bond is readily bound to CO_2 and favourable for CO_2RR , while breakage of the Au–S bond leads to the exposure of the metal site, which is preferable for HER. Recognition of the real catalytic site in the two studies perfectly reflects the advantages of atomically precise NCs in revealing the catalytic mechanism and exploring the relationship between structure and activity.

In a comparison of CO_2RR performance between $\text{Pd}_1\text{Au}_{24}(-\text{SR})_{18}$ and $\text{Au}_{25}(\text{SR})_{18}$ NCs ($\text{R} = -\text{CH}_2\text{CH}_2\text{Ph}$), Li *et al.* found that $\text{Pd}_1\text{Au}_{24}$ can greatly improve the CO_2RR selectivity, with $\sim 100\%$ FE_{CO} , especially at high potential (up to -1.2 V), while the FE_{CO} of Au_{25} NCs starts to decrease at -0.9 V.¹⁵¹ Theoretical calculations demonstrate that the surface S atom is the active site, and $\text{Pd}_1\text{Au}_{24}$ can increase the thermodynamic barrier for ligand removal and retain a larger population of S active sites compared to Au_{25} , which contributes to the improved CO_2RR selectivity in the extended potential range. As Pd doping can effectively improve the activity of Au NCs in CO_2RR , it is natural to think of two-element doping to form trimetallic Au-based NCs. Zhuang *et al.* utilized the AGR method to synthesize $\text{Au}_3\text{-AgPd}_6(\text{TBBT})_{12}$ NCs by introducing a kernel Ag single atom on the basis of $\text{Au}_4\text{Pd}_6(\text{TBBT})_{12}$.¹⁵² The trimetallic Au_3AgPd_6 NCs show higher CO_2RR activity and selectivity than Au_4Pd_6 with a similar structure (Fig. 6c). The introduction of Ag causes a significant change in electronic structure, decreases the d-center, weakens $^*\text{CO}$ adsorption, and promotes the release of CO, thereby improving the CO_2RR activity. Meanwhile, the difficulty of $^*\text{H}$ desorption is increased, suppressing HER and enhancing CO_2RR selectivity. Pd doping can not only enhance the activity of CO_2RR but also shows the ability to change product type. Cai *et al.* prepared Au-based NCs (Au_9 and Au_8Pd_1) confined in a layer of montmorillonite to form NC-based heterogeneous catalysts.¹⁵³ Pd doping can reduce the propensity for structural variation induced by the change in coordination number of the surface Au site during the reaction, bringing about multiple benefits to the catalysis. In a traditional fixed-bed reactor, Au_8Pd_1 exhibits unique catalytic performance



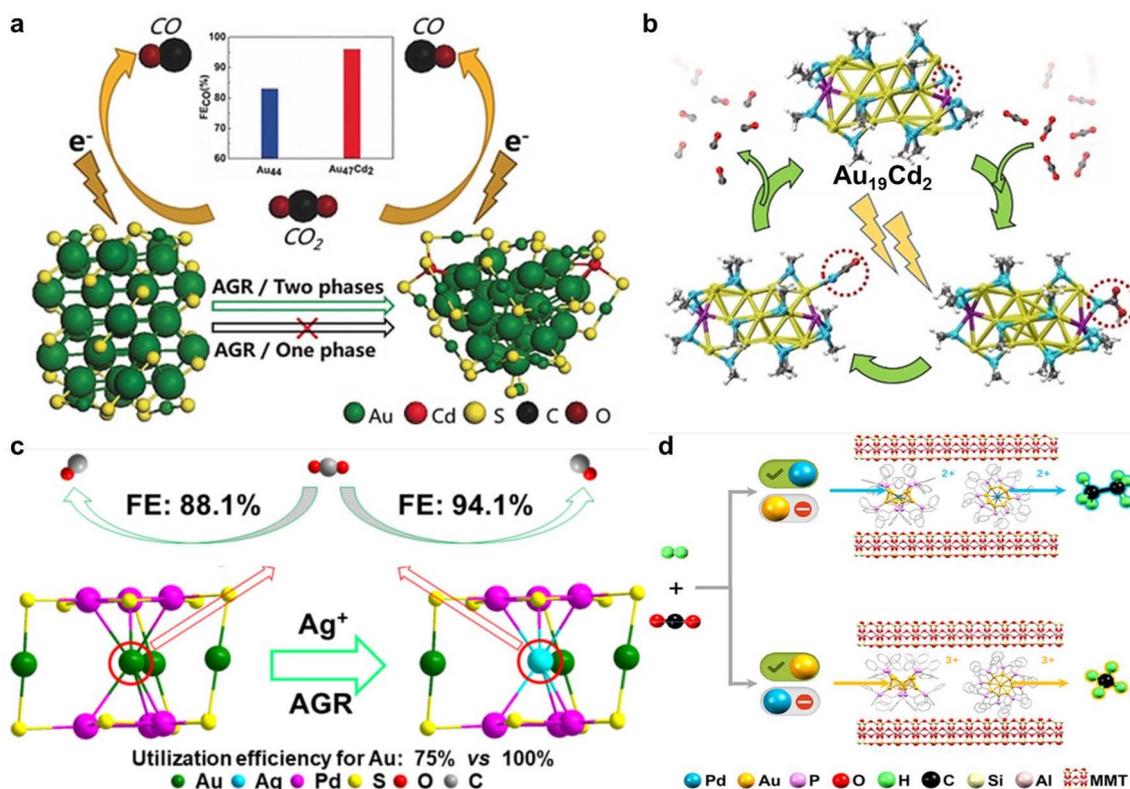


Fig. 6 (a) Schematic diagram of the synthesis and comparison of the CO₂RR activity of Au₄₄ and Au₄₇Cd₂ NCs. Reproduced from ref. 148 with permission from Wiley-VCH, copyright 2020. (b) Schematic diagram of the structural dynamic evolution of Au₁₉Cd₂ during CO₂RR. Reproduced from ref. 149 with permission from Wiley-VCH, copyright 2021. (c) Synthesis scheme and comparison of the CO₂RR activity of Au₄Pd₆ and Au₃AgPd₆ NCs. Reproduced from ref. 152 with permission from American Chemical Society, copyright 2022. (d) Schematic diagram of tuning selectivity in CO₂ catalytic conversion by Au₉ and Au₈Pd₁ NCs. Reproduced from ref. 153 with permission from Chinese Chemical Society, copyright 2021.

in the CO₂ hydrogenation reaction, changing the product type from methane to ethane, and improving the catalytic stability as well (Fig. 6d).

Many reports have also shown that AuAg alloy NCs are a highly efficient electrocatalyst for CO₂RR. Seong *et al.* developed an active-site transplantation strategy to synthesize core-shell AuAg₁₂@Au₁₂(SETPh)₁₈ NCs (SETPh = 2-phenylethanethiolate) by replacing the Ag₁₂(SR)₁₈ shell of Ag₂₅(SR)₁₈ NCs with an Au₁₂(SR)₁₈ shell.¹⁵⁴ Compared to Ag₂₅(SR)₁₈ NCs, the active-site-engineered AuAg₁₂@Au₁₂(SETPh)₁₈ NCs show significantly improved CO₂RR activity with a 200 mA cm⁻² industry current density and a 2.1 V full-cell potential in a zero-gap CO₂-to-CO electrolyzer. Lin *et al.* prepared AuAg₂₆(SAdm)₁₈S⁻ (HSAdm = 1-adamantanethiolate) NCs composed of an AuAg₁₂ icosahedron kernel and an Ag₁₄(SR)₁₈S open shell.¹⁵⁵ Unlike Ag₂₅(DMT)₁₈⁻ (DMT = 2,4-dimethylbenzenethiol) and Au₂₁(SAdm)₁₆ with a closed shell, due to the open shell structure in AuAg₂₆(SAdm)₁₈S⁻, the partial Ag atoms of the AuAg₁₂ kernel are not protected by thiols, resulting in the exposure of some facets of the kernel. Therefore, owing to the unique open shell structure and Au-Ag synergistic effect, AuAg₂₆ exhibits lower *COOH formation free energy and displays increased CO₂RR activity (98.4% FE_{CO} at -0.97 V), compared to Ag₂₅ and Au₂₁ NCs (Fig. 7a). Based on the superior CO₂RR activity of AuAg alloy

NCs, Li *et al.* further investigated the effect of the accessibility of metal sites on the CO₂RR performance by systematically studying a series of alkynyl-protected AuAg NCs (Au_nAg_{46-n}(C≡CR)₂₄Cl₄(PPh₃)₂, Au₂₄Ag₂₀(C≡CR)₂₄Cl₂, and Au₄₃(C≡CR)₂₀/Au₄₂Ag₁(C≡CR)₂₀) of similar size and structure but different surface ligand coverage.¹⁵⁶ Among these NCs, Au₄₃(C≡CR)₂₀ and Au₄₂Ag₁(C≡CR)₂₀ with the highest number of accessible metal sites exhibit the highest FE_{CO} (Fig. 7b). Xu *et al.* utilized two AuAg alloy NCs (Au₂₄Ag₂₀ and Au₄₃Ag₃₈) to explore how the hierarchical assembly influences CO₂RR activity.¹⁵⁷ There are some correlations and differences between the two NCs, such as Au₄₃Ag₃₈ maintaining the kernel framework from the parent Au₂₄Ag₂₀ and it can be regarded as a dimeric form of Au₂₄Ag₂₀ monomeric NCs; Au₂₄Ag₂₀ is racemic, while Au₄₃Ag₃₈ is mesomeric; Au₂₄Ag₂₀ exhibits superatomic electronic configurations, while Au₄₃Ag₃₈ has molecule-like characteristics. Possibly due to the different atomic packing structures (individual-core *vs.* dual-core) and surface motif arrangement (parallel *vs.* crossed), the Au₂₄Ag₂₀ monomers show better CO₂RR activity than Au₄₃Ag₃₈ dimers.

Cu is considered as a special element for CO₂RR due to the suitable adsorption energy for *CO and *CH_xO intermediates; therefore Cu-doped Au NCs have received a lot of attention. Deng *et al.* synthesized [Au₁₅Cu₄(DPPM)₆Cl₄(C≡CR)₁]²⁺ NCs



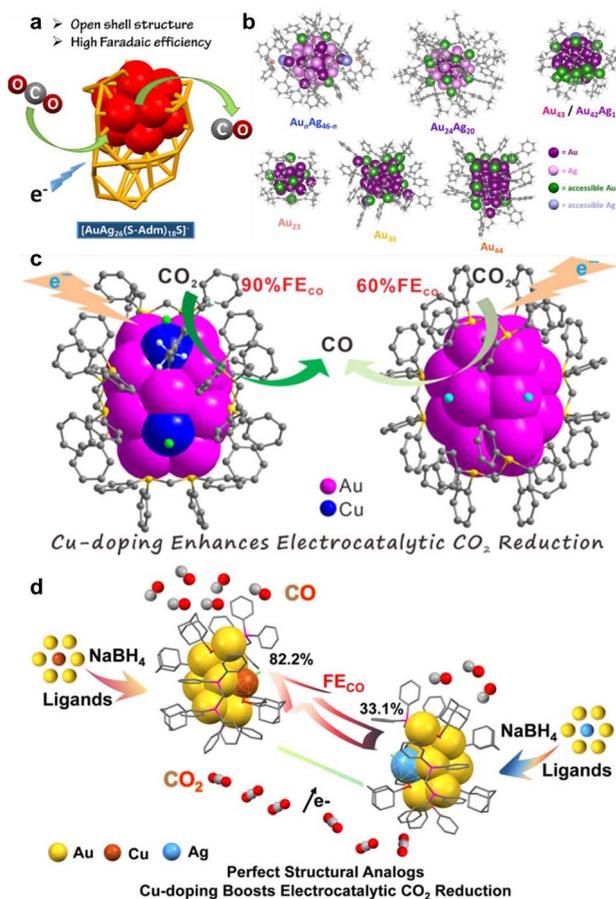


Fig. 7 (a) Schematic diagram of open shell structure of AuAg₂₆(-SAdm)₁₈S⁻ for enhanced CO₂RR activity. Reproduced from ref. 155 with permission from American Chemical Society, copyright 2021. (b) The metal sites accessible to CO₂ on the surface of different Au/Ag NCs. Reproduced from ref. 156 with permission from Royal Chemical Society, copyright 2023. (c) Schematic diagram of Au₁₅Cu₄-enhanced CO₂RR activity compared to Au₁₈ NCs. Reproduced from ref. 158 with permission from American Chemical Society, copyright 2023. (d) Comparison of CO₂RR activity of structural analogs of Au₈Cu₁ and Au₈Ag₁ NCs. Reproduced from ref. 160 with permission from Wiley-VCH, copyright 2024.

(DPPM = bis(diphenylphosphino)methane; HC≡CR = 3,5-bis-(trifluoromethyl)phenylacetylene) *via* a one-pot method.¹⁵⁸ Compared to the monometallic structural analogue, [Au₁₈(-DPPM)₆Br₄]²⁺, Au₁₅Cu₄ shows a dramatic enhancement in CO₂RR activity with a high FE_{CO} of >90% and an up to industrial CO partial current density of -413 mA cm⁻² at -3.75 V in a membrane electrode assembly (MEA) cell (Fig. 7c). The exposed Au-Cu dual sites synergistically modulate the d-state shift, contributing to the enhanced catalytic activity. Ding *et al.* also explored the Au-Cu synergistic effect on CO₂RR activity.¹⁵⁹ They found that Au₁Cu₂₄ NCs are preferable for the CO₂RR, while Cu₂₅ NCs tends to progress HER, because AuCu synergy can effectively suppress HER due to the contracted electronic distribution. Based on the single Cl-terminated coordination strategy, Su *et al.* obtained a pair of structural analogs, [Au₈Ag₁(SAdm)₄(Dppm)₃Cl]²⁺ and [Au₈Cu₁(SAdm)₄(-Dppm)₃Cl]²⁺.¹⁶⁰ Due to the same overall structure and metal

doping number and position, the metal doping type effect can be decoupled from various entangled influencing factors to elucidate metal synergies solely in terms of atomic differences. Au₈Cu₁ shows higher FE_{CO} than Au₈Ag₁ due to the generation of thermodynamically more stable *COOH and lower *CO formation energy (Fig. 7d). The rare structural analogs help us clearly reveal the impact of single-metal change on the catalytic performance. Doping a foreign metal atom to form Au-based alloy NCs can not only regulate the electronic and geometric structure to enhance catalytic activity but also minimize Au usage and reduce the catalyst cost when doping with non-precious metal atoms. Seong *et al.* developed a highly-efficient and economic CO₂RR catalyst with high mass activity, Au₄Ni₂ NCs, by the transplantation of Au active sites into non-precise Ni₄ NCs (Fig. 8a).¹⁶¹ In Au₄Ni₂ NCs, the Au atoms are the active sites, the Ni atoms mainly play the role of a cost reducer, and thereby the utilization efficiency of the Au atoms is improved. The TOF and mass activity of Au₄Ni₂ NCs for CO₂-to-CO are 206 mol_{CO} mol_{NC} s⁻¹ and 25228 A/g_{Au}, respectively.

For CO₂RR, the activation of CO₂ is critical because it is the first step in CO₂ conversion. CO₂ is a linear molecule with high stability, resulting in difficulty in its activation.¹⁶² Constructing asymmetric charge distribution sites is an effective way to activate CO₂,^{163,164} and our previous review introduced several strategies of symmetry-breaking sites in metal NCs for enhancing CO₂RR activity, including a heteroatom doping induced strategy.¹⁶⁵ For example, Tan *et al.* synthesized a series of Au₁₃Cu_x alloy NCs (x = 0-4) with different degrees of symmetry-breaking on the crystal structure by manipulating Cu atom doping (Fig. 8b).¹⁶⁶ Au₁₃Cu₁, Au₁₃Cu₂, and Au₁₃Cu₄ have C_{3v} symmetry, C_{3h} symmetry, and T_d symmetry, respectively, while Au₁₃Cu₃ exhibits an asymmetric surface structure with 2 three-coordinate

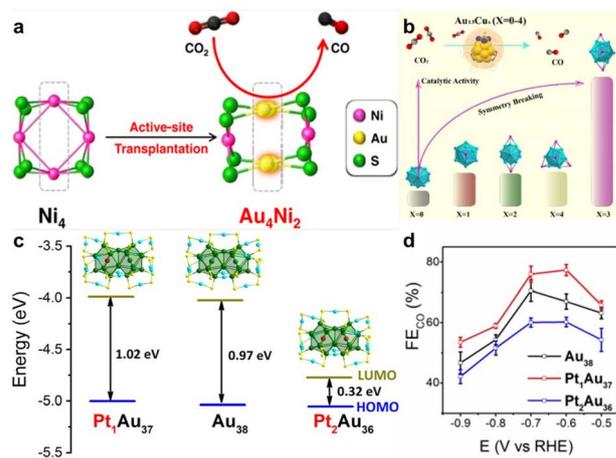


Fig. 8 (a) Schematic diagram of active site transplantation from Ni₄ to Au₄Ni₂ NCs for enhanced CO₂RR. Reproduced from ref. 161 with permission from American Chemical Society, copyright 2023. (b) Schematic diagram of the different degrees of symmetry breaking in Au₁₃Cu_x (x = 0-4) NCs for different CO₂RR performances. Reproduced from ref. 166 with permission from Wiley-VCH, copyright 2024. (c) Electronic structure energy level and (d) comparison of CO₂RR activity of Au₃₈, Pt₁Au₃₇, and Pt₂Au₃₆. Reproduced from ref. 167 with permission from Wiley-VCH, copyright 2022.



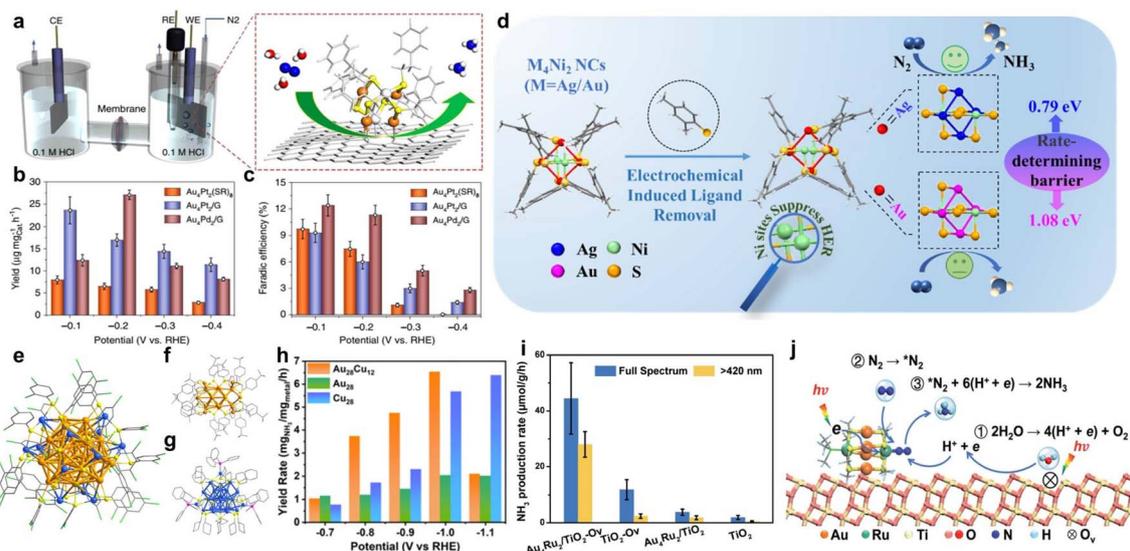


Fig. 9 (a) Schematic diagram of $\text{Au}_4\text{M}_2/\text{G}$ ($\text{M} = \text{Pt}, \text{Pd}$) for NRR. (b) NH_3 yield rate and (c) FE of NH_3 comparison of Au_4Pt_2 NC and $\text{Au}_4\text{M}_2/\text{G}$ ($\text{M} = \text{Pt}, \text{Pd}$). Reproduced from ref. 176 with permission from Springer Nature, copyright 2020. (d) Schematic diagram of regulation of intrinsic activity of M_4Ni_2 ($\text{M} = \text{Au}, \text{Ag}$) NCs for NRR. Reproduced from ref. 177 with permission from Wiley-VCH, copyright 2022. (e) Structure of $\text{Au}_{28}\text{Cu}_{12}$, (f) Au_{28} , and (g) Cu_{28} NCs. (h) NH_3 yield rate comparison of $\text{Au}_{28}\text{Cu}_{12}$, Au_{28} , and Cu_{28} NCs. Reproduced from ref. 181 with permission from Royal Chemical Society, copyright 2024. (i) NH_3 yield rate of $\text{Au}_4\text{Ru}_2/\text{TiO}_2\text{-O}_v$, $\text{TiO}_2\text{-O}_v$, $\text{Au}_4\text{Ru}_2/\text{TiO}_2$, and TiO_2 under different sources of light irradiation. (j) Proposed mechanism for photocatalytic NRR on $\text{Au}_4\text{Ru}_2/\text{TiO}_2\text{-O}_v$. Reproduced from ref. 182 with permission from Royal Chemical Society, copyright 2020.

Cu_1S_3 and 1 two-coordinate Cu_1S_2 motifs. With the highest asymmetry degree of $\text{Au}_{13}\text{Cu}_3$, the unsaturated Cu_1S_2 site on the surface more readily coordinates with CO_2 , promoting CO_2 adsorption and CO_2RR activity. As a result, $\text{Au}_{13}\text{Cu}_3$ shows the highest current density of 70 mA cm^{-2} within the $\text{Au}_{13}\text{Cu}_x$ family of NCs ($\text{Au}_{13}\text{Cu}_x$ ($x = 1, 2, 4$): 40 mA cm^{-2} , and Au_{13} : 15 mA cm^{-2}). In addition, Liu *et al.* obtained identical geometric structural $\text{Pt}_1\text{Au}_{37}(\text{SR})_{24}$ and $\text{Pt}_2\text{Au}_{36}(\text{SR})_{24}$ ($\text{SR} = 4\text{-tert-butylbenzyl mercaptan}$) by the controllable asymmetrical and symmetrical doping of Pt atoms into parent $\text{Au}_{38}(\text{SR})_{24}$ NCs.¹⁶⁷ The structure of $\text{Pt}_1\text{Au}_{37}$ is that one Pt atom asymmetrically dopes into one of the two cores of Au_{38} , and relative to Au_{38} , $\text{Pt}_1\text{Au}_{37}$ displays higher HOMO energy with the loss of one valence electron. While the two Pt atoms in $\text{Pt}_2\text{Au}_{36}$ are symmetrically located in the two cores of Au_{38} , and $\text{Pt}_2\text{Au}_{36}$ exhibits a narrowed HOMO–LUMO gap and loses two valence electrons, compared to Au_{38} (Fig. 8c). The difference in doping mode causes the modulation of electronic structure; thereby, $\text{Pt}_1\text{Au}_{37}$ shows high electron-spin-induced CO_2RR activity, followed by Au_{38} and $\text{Pt}_2\text{Au}_{36}$ (Fig. 8d). Besides, Wang *et al.* utilized an Fe single atom (SA) site to modify Au_8 NCs and integrate SA and NC into one system.¹⁶⁸ Due to the introduction of Fe SA, asymmetric charge distributed active sites are constructed and the key intermediate $^*\text{COOH}$ adsorption energy is optimized to benefit an improvement in CO_2RR activity, leading to ~ 18.07 -fold amplification in the FE of CO_2 -to- CO compared to isolated Au_8 NCs.

3.6 Au-based bimetallic NCs in the synthetic ammonia reaction

Ammonia is an important industrial raw material that plays an important role in the manufacture of fertilizers, dyes, and

pharmaceuticals. In addition, due to its large hydrogen capacity, high energy density, and ease of transportation, ammonia is considered a potential carbon-free fuel.^{169–171} The traditional Haber–Bosch process enables the large-scale industrial production of ammonia, but its production conditions ($400\text{--}550 \text{ }^\circ\text{C}$, $15\text{--}30 \text{ MPa}$) are harsh and are associated with high energy consumption and CO_2 emissions.^{172–174} Using sustainable electric energy, solar energy and other new energy sources as the driving force, abundant N_2 in the atmosphere or environmentally harmful but highly active nitrogen-containing species (such as NO , $\text{NO}_2^-/\text{NO}_3^-$) are reduced to synthesize ammonia under conditions of ambient temperature and pressure, which is considered to have great application potential.^{20,175}

Yao *et al.* firstly synthesized Pt/Pd-doped Au-based NCs ($\text{Au}_4\text{M}_2(\text{SR})_8$, $\text{M} = \text{Pd}/\text{Pt}$) with a precise and controllable size distribution and metal doping and then removed partial ligands by thermal treatment to anchor it onto defective graphene to create a robust supported NC-based catalyst (Fig. 9a).¹⁷⁶ DFT calculations indicate that heteroatom doping plays an essential role in N_2 activation *via* enhanced electron back donation to N_2 antibonding π^* -orbitals. By precise metal doping, Au_4Pd_2 shows higher FE_{NH_3} and NH_3 yield at -0.2 V than Au_4Pt_2 in the electrocatalytic N_2 reduction reaction (NRR) (Fig. 9b and c). From the perspective of tuning intrinsic catalytic activity of NCs, Han *et al.* introduced non-precise metal Ni with the ability to suppress HER (the competitive reaction to NRR) to prepare M_4Ni_2 ($\text{M} = \text{Au}/\text{Ag}$) NCs.¹⁷⁷ Compared to monometallic NCs (Au_6 , Ag_6 , and Ni_6), bimetallic M_4Ni_2 ($\text{M} = \text{Au}/\text{Ag}$) shows better NRR performance. On the one hand, the superior NRR activity is attributed to the effective inhibition of HER by the introduction



of Ni. On the other hand, partial ligand detachment during the electrochemical process provides exposed active sites to access more N_2 reactant and induces reconstruction of the electronic structure, benefiting the NRR (Fig. 9d).

It has been reported that Cu is considered to be a promising candidate for electrocatalytic NO_3^- reduction (NO_3RR) to NH_3 .¹⁷⁸ However, Cu is prone to surface poisoning due to spontaneous oxidative dissolution as well as easy adsorption of other species in the electrolyte.^{179,180} Tang *et al.* doped Cu atoms on the surface of Au_{28} NCs to form stable AuCu alloy NCs ($Au_{28}Cu_{12}(SR)_{24}(PPh_4)_4$ ($SR = 2,4$ -dichlorothiophenol)).¹⁸¹ Due to the synergistic effect between Au and Cu, the geometric and electronic structure of $Au_{28}Cu_{12}$ are tailored to be suitable for NO_3RR . Compared to monometallic $Au_{28}(TBBT)_{20}$ ($TBBT = 4$ -*tert*-butylbenzenethiol) and $Cu_{28}(CHT)_{18}(PPh_3)_3$ ($CHT =$ cyclohexanethiol), bimetallic $Au_{28}Cu_{12}$ shows higher NH_3 production activity and stability (Fig. 9e–h).

Sun *et al.* first screened the feasibility of light-driven NRR by a series of Au_n NCs ($n = 8, 9, 11, 18, 23, 24, 25, 28, 36, 44$).¹⁸² Due to the physical adsorption of N_2 on the surface of Au_n (the distance between N_2 and Au_n is longer than 3.2 Å), it is impossible for N_2 to coordinate to Au_n for activation. Considering Ru is a recognized NRR candidate, Ru-doped Au NCs ($Au_4Ru_2(-PPh_3)_2(SC_2H_4Ph)_8$) are synthesized and then loaded onto the oxygen vacancies of TiO_2 to form an NC-based heterogeneous photocatalyst (Au_4Ru_2/TiO_2-O_v) (Fig. 9i). Under light irradiation, both Au_4Ru_2 NCs and TiO_2 can directly generate e–h pairs and photoinduced electron transfer from TiO_2 to Au_4Ru_2 NCs. The introduction of Ru atoms can effectively promote electron injection to adsorbed N_2 and then realize N_2 activation (Fig. 9j). The supported bimetallic Au_4Ru_2 NCs displays better photocatalytic NRR activity than homogold Au_n NCs (Fig. 9i). This work not only indicates the ability for light harvesting and photogenerating e–h pairs over NCs with non-metallic or excitonic behavior, but also demonstrates a cooperative effect based on heteroatom doping.

4. Summary and outlook

Metal NCs not only act as a bridge connecting metal NPs and SACs in terms of their size aspect, it also compensates for their shortcomings in catalysis as a unique type of nanomaterial. First of all, from the perspective of electronic structure, metal NCs have discrete electronic energy levels unlike metal NPs and SACs, and therefore, they show distinctive performance in catalysis. Secondly, compared to metal NPs, the size of the metal NCs is smaller, their atomic utilization is higher, and the number of surface unsaturated coordinated active sites is richer. In addition, the molecule-like high purity and homogeneity in size, composition, structure, and surface environment of atomically precise metal NCs provides the opportunity to reveal the catalytic mechanism and guide catalyst design at the atomic level, which is impossible for metal NPs to achieve. Compared to SACs, metal NCs can effectively exert a synergistic effect between metal atoms, adjusting the composition, geometric configuration and electronic structure of the catalyst,

to realize “1 + 1 > 2” enhancement of catalytic activity, selectivity and stability.

In the metal NC family, Au-based NCs not only exhibit the advantages of simple synthesis, high yield, and easy functionalization but also possess the characteristics of high stability and solubility in various solvents, therefore attracting lots of attention from catalysis researchers. Unlike previous reviews on alloy NCs and NC catalysis (either focusing on the controllable synthesis of NCs or involving general catalytic reactions), this perspective aims at the unsatisfactory activity and dilemma about the unclear reaction mechanism facing the energy-related small-molecule catalytic reaction at the present stage, mainly summarizing the synergistic effect on an enhancement in catalytic performance in atomically precise Au-based bimetallic NCs. From the above summary and discussion, great efforts have been made in this field, and gratifying developments and advances have been achieved. Finally, in this section, some of our own perspectives and insights are put forward, to promote further development, innovation and breakthroughs in this field in the future.

(1) The synthesis range of doped metal NCs needs to be further expanded. It is not limited to bimetallic NCs. At present, there have been reports on trimetallic alloy NCs. We can learn from ideas about the preparation of high-entropy alloy NPs,^{183,184} to try to synthesize polymetallic alloy NCs, and perhaps some novel and unexpected phenomena or properties will appear in the subnanometer region. In addition, as far as synthesis is concerned, the rapid development of society no longer allows us to continue to blindly use the “trial and error” approach, which is too inefficient. We can use the advanced scientific and technological achievements of computer science, allowing chemistry, catalysis, computer technology and other interdisciplinary subjects to cross-fertilise and integrate, use artificial intelligence to predict the kind of doping, the amount of doping, and the position of doping for the best catalytic performance, which can greatly improve preparation efficiency.^{185,186} Additionally, they can be combined with a high-throughput NC synthesis technique to quickly prepare multiple types of NCs at one time in order to quickly screen their catalytic properties.¹⁸⁷

(2) Considering future practical application scenarios, the cost-effectiveness of catalysts is an important consideration. It is necessary to develop non-noble metal clusters, such as transition metal clusters (iron-based, cobalt-based, nickel-based, copper-based clusters, *etc.*). However, due to their inherent instability (easily reacting with oxygen and water), the synthesis conditions are relatively harsh, and the purity and yield of the obtained product are unsatisfactory. Therefore, it is necessary to choose more suitable protective ligands to stabilize the transition metal core. In addition, synthesis can also be considered in an anhydrous and oxygen-free environment in a glove box. The large-scale preparation of cluster-based catalysts also needs to be given attention. Currently, chemical synthesis methods are relatively mature, and there are many types of clusters that can be prepared by this method, and high-purity and high-yield products can be obtained through precise control over chemical reaction conditions. However, the synthesis of cluster-based catalysts is still in the laboratory stage, and there are only a few



reports in the literature where the yield of one-time synthesis reaches the gram level.^{188–191} There is still a long way to go to achieve industrial-scale preparation. Furthermore, for the recycling and recovery of clusters after catalytic reaction, one strategy with the most potential and promise is the construction of cluster-based composites. Due to the small size of the clusters, a support is required to load them, while avoiding aggregation or mass loss after the reaction. Porous materials are good candidates due to their abundant and adjustable pores and channels. If the surface of the material could be modified with various functional groups, it would be even better because it could solidly connect with clusters, and various types of surface groups may also bring about unexpected improvements in catalytic performance.

(3) For bimetallic NCs, and even for polymetallic NCs that may be used in the future, the enhancement in their catalytic performance is mainly attributed to the synergistic effect between metal atoms, but this statement is very general. Specifically, it is not particularly clear how the components affect each other or regulate each other, and how they play a synergistic role. Do the different metal atoms regulate each other's electronic structure, jointly affect the adsorption, activation and desorption behaviour of reaction molecules/intermediates/product molecules, and then realize synergistic catalysis? or is it tandem/cascade catalysis? for example, in CO₂RR, in an Au–Cu alloy, the Au site usually plays the role of converting CO₂ into CO, and then CO reduction and coupling continue to occur at the Cu site, achieving efficient tandem/cascade catalysis.¹⁹² This is a scientific question worthy of detailed discussion and careful investigation.

(4) An NC is a complex system involving an inner core of metal atoms and outer organic ligands, each of which plays a role in catalysis. In some catalytic cases, it has been found that it is not only the surface atoms that participate in the catalytic reaction; even the metal atoms at the center of the metal core also contribute to catalysis.^{153,167} Additionally, in cases of the Au–Cd NCs catalysis of CO₂RR, the real catalytically active center (the exposed Au site with –SR detachment, or the exposed S site with –R removal) has been investigated in detail.^{149,150} All these inspire us to make more careful explorations in the future to determine the real active sites. In addition, for an expansion of types of energy catalysis, especially those involving multiple reactants and

steps, it will be meaningful and useful to clarify the real role each component plays in catalysis to guide catalyst design in the future.

(5) Although most current energy catalytic reactions are still laboratory-level, the future will certainly tend toward industrialization, and there are already some reports about HER, ORR, CO₂RR, *etc.* at industrial current density at this stage.^{193–195} As mentioned above, using NCs alone still faces the problem of easy aggregation and declining activity. Therefore, in industrial catalysis, functional supports are needed to load NCs to strengthen their stability and increase service lifetime. Therefore, it is necessary to clarify the interface and interaction between NCs and supports, so as to purposefully select appropriate supports and form supported NC-based catalysts with high activity for target reactions.

Overall, atomically precise bimetallic NCs have unique advantages in energy-related catalysis not only reflecting their extraordinary activity but also providing the opportunity to build structure–activity correlation; therefore, it deserves much more effort for further in-depth exploration and wide application, and the insights and general rules obtained from it that can be extended to other alloy materials and more types of catalytic reaction in the future.

Data availability

All data in this perspective were cited from other references.

Author contributions

Y. X. Du and M. Z. Zhu conceived the topic and structure of the article. Y. Fang and P. Wang conducted the literature research and designed the figures and tables. All authors were responsible for reviewing, editing and developing the perspective.

Conflicts of interest

The authors have no competing interests to declare.

Appendix

Table 1 Summary of representative Au-based bimetallic NCs

Series NC _s name	NC _s formula	Synthesis method	Structural characteristic			Reference
			Doping type	Doping number	Doping position	
M ₁ Au ₃ series NCs	[(Audppy) ₃ AgO](BF ₄) ₂	Metal-exchange strategy	Ag	1	Kernel surface doping	196
M ₂ Au ₄ series NCs	Au ₄ Ni ₂ (PPh ₂) ₂ S ₂ (PCP) ₂	Direct co-reduction strategy	Ni	2	Kernel surface doping	197
	Au ₄ Pd ₂ (SR) ₈ , SR = SC ₂ H ₄ Ph	Direct co-reduction strategy	Pd	2	Kernel surface doping	105
	Pt ₂ Au ₄ L ₈ , L = C ₂₁ H ₂₈ O ₂	Direct co-reduction strategy	Pt	2	Kernel surface doping	198



Table 1 (Contd.)

Series NC _S name	NC _S formula	Synthesis method	Structural characteristic			Reference
			Doping type	Doping number	Doping position	
M ₄ Au ₄ series NCs	[Au ₄ Cu ₄ (π-CH≡Cp-C ₆ H ₄ R)], R = H, Cl, CH ₃	Direct co-reduction strategy	Cu	4	Kernel surface doping	199
	Au ₄ Cd ₄ (2, 4-DMBT) ₁₂	Cation-assisted strategy	Cd	4	Kernel surface doping	200
	[Au ₄ Cu ₄ (DPPM) ₂ (S-Adm) ₅] ⁺ Br ⁻	Direct co-reduction strategy	Cu	4	Kernel surface doping	201
M ₂ Au ₆ series NCs	[Au ₆ Ag ₂ (C)(L ₂) ₆](BF ₄) ₄ , L ₂ = 2-(diphenylphosphino)-5- pyridinecarboxaldehyde	Direct co-reduction strategy	Ag	2	Kernel surface doping	202
	[Au ₆ Ag ₂ C(dppy) ₆](BF ₄) ₄	Direct co-reduction strategy	Ag	2	Kernel surface doping	203
M ₆ Au ₂ series NCs	Au ₂ Cu ₆ (PPh ₂ Py) ₂ (S-Adm) ₆ ,	Direct co-reduction strategy	Cu	6	Kernel surface doping	204
	Au ₂ Cu ₆ (PPh ₂ Py) ₂ (TBM) ₆	Direct co-reduction strategy	Cu	6	Kernel surface doping	205
	Au ₂ Cu ₆ (S-Adm) ₆ (P(Ph-OMe) ₃) ₂ , Au ₂ Cu ₆ (S-Adm) ₆ (PPh ₃) ₂ , Au ₂ Cu ₆ (S-Adm) ₆ (P(Ph-F) ₃) ₂	Direct co-reduction strategy	Cu	6	Kernel surface doping	205
(M-Au) ₉ series NCs	[PdAu ₈ (PPh ₃) ₈] ²⁺	Direct co-reduction strategy	Pd	1	Center doping	206
	Au ₄ Ag ₅ (dppm) ₂ (S-Adm) ₆ (BPh ₄)	Direct co-reduction strategy	Ag	5	Kernel surface doping	207
(M-Au) ₁₀ series NCs	Au ₄ Pd ₆ (TBBT) ₁₂	Direct co-reduction strategy	Pd	6	Kernel surface doping	152
	[PdAu ₉ H(PPh ₃) ₈ Cl] ⁺	Direct co-reduction strategy	Pd	1	Center doping	208
(M-Au) ₁₂ series NCs	[Au ₁₀ Ag ₂ (2-py-C= C) ₃ (dppy) ₆](BF ₄) ₅	Direct co-reduction strategy	Ag	2	Kernel surface doping	209
	[Au ₁₁ Cu ₁ (PPh ₃) ₇ (SPy) ₃] ⁺	Direct co-reduction strategy	Cu	1	Kernel surface doping	210
	Au ₆ Cu ₆ MBT ₁₂ , Au ₆ Cu ₆ PET ₁₂ AuCu ₁₁ [S ₂ P(OiPr) ₂] ₆ (C≡CPh) ₃ Cl	Metal-exchange strategy Intercluster reaction strategy	Cu Cu	6 11	Kernel surface doping Kernel surface doping	211 212
(M-Au) ₁₃ series NCs	[AuCu ₁₂ (SR) ₆ (C≡CPh) ₄] ⁺ , SR = S ₂ P(C ₂ H ₄ Ph) ₂	Direct co-reduction strategy	Cu	12	Kernel doping	213
(M-Au) ₁₅ series NCs	[Au ₇ Ag ₈ (^t BuC≡C) ₁₂] ⁺	Direct co-reduction strategy	Ag	8	Kernel surface doping	214
(M-Au) ₁₆ series NCs	[Au ₇ Ag ₉ (dppf) ₃ (CF ₃ CO ₂) ₇ BF ₄] _n	Direct co-reduction strategy	Ag	9	Kernel surface doping, Motif doping	215
Au ₁₃ Cu _x series NCs	[Au ₁₃ Cu ₄ (PPh ₂ Py) ₄ (SC ₆ H ₄ - <i>tert</i> - C ₄ H ₉) ₈] ⁺	Intercluster reaction strategy	Cu	4	Motif doping	216
	Au ₁₃ Cu ₄ (PPh ₂ Py) ₃ (SePh) ₉	Direct co-reduction strategy	Cu	4	Motif doping	217
	[Au ₁₃ Cu ₂ (DPPP) ₃ (SPy) ₆] ⁺	Direct co-reduction strategy	Cu	2	Motif doping	218
	[Au ₁₃ Cu ₂ (PPh ₃) ₆ (SPy) ₆] ⁺	Intercluster reaction strategy	Cu	2	Motif doping	216
(M-Au) ₁₇ series NCs	Au ₁₆ Ag ₁ (S-Adm) ₁₃	Direct co-reduction strategy	Ag	1	Center doping	219
	Au ₄ Ag ₁₃ (DPPM) ₃ (SR) ₉ , SR = C ₈ H ₁₀ S	Direct co-reduction strategy	Ag	13	Kernel surface doping, Motif doping	220
	Au _x Ag _{17-x} N ₃ (TBBT) ₁₂ , N = a counter cation, x = 0, 1	Direct co-reduction strategy	Ag	16, 17	Kernel doping	221
(M-Au) ₁₈ series NCs	Au ₁₅ Ag ₃ (SR) ₁₄ SR=SC ₆ H ₁₁	Intercluster reaction strategy	Ag	3	Kernel surface doping	222
	[Ag _x Au _{18-x} (Dppm) ₆ Br ₄](BPh ₄) ₂ (x = 1, 2)	Metal-exchange strategy	Ag	1, 2	Kernel surface doping	223
(M-Au) ₁₉ series NCs	[Au ₇ Cu ₁₂ (dppy) ₆ (TBBT) ₆ Br ₄] ³⁺	Direct co-reduction strategy	Cu	12	Kernel surface doping	224



Table 1 (Contd.)

Series NC _S name	NC _S formula	Synthesis method	Structural characteristic			Reference
			Doping type	Doping number	Doping position	
(M–Au) ₂₁ series NCs	[Au ₁₉ Cd ₂ (SR) ₁₆] [−] , SR = C ₆ H ₁₁ S	Direct co-reduction strategy	Cd	2	Motif doping	225
	[Au ₉ Ag ₁₂ (SR) ₄ (dppm) ₆ X ₆] ³⁺ , SR = S-Adm/S [−] Bu, X = Cl/Br	Direct co-reduction strategy	Ag	12	Kernel surface doping, Motif doping	226
	Au ₂₀ Ag ₁ (S-Adm) ₁₅	Direct co-reduction strategy	Ag	1	All	227
	Au ₂₀ Ag ₁ (SR) ₁₅ , Au _{21−x} Ag _x (SR) ₁₅ (x = 4–8), Au _{21−x} Cu _x (SR) ₁₅ (x = 0–5), SR = SC ₄ H ₁₀ O	Direct co-reduction strategy	Ag, Cu	0–8	Kernel surface doping/ Motif doping	228
(M–Au) ₂₃ series NCs	Au _{23−x} Cu _x (SR) ₁₆ , SR = SC ₆ H ₁₂ O	Direct co-reduction strategy	Cd	2	Motif doping	225
M ₁ Au ₂₄ series NCs	[Au ₂₄ Pd(PPh ₃) ₁₀ (SR) ₅ Cl ₂], SR = SC ₂ H ₄ Ph	Direct co-reduction strategy	Pd	1	Center doping	229
	Au ₂₄ M ₁ (SR) ₁₈ , SR = SC ₂ Ph/PET	Direct co-reduction strategy	Hg, Cd, Pt, Pd	1	Kernel surface doping/ Center doping	230–232
M ₂₄ Au ₁ series NCs	[Ag ₂₄ Au(SR) ₁₈] [−] PPh ₄ ⁺ , SR = SPhMe ₂	Direct co-reduction strategy	Ag	24	Kernel surface doping, Motif doping	233
	[Au ₁ Ag ₂₄ (Dppm) ₃ (SR) ₁₇] ²⁺ , SR = C ₆ H ₁₂ S	Direct co-reduction strategy	Ag	24	Kernel surface doping, Motif doping	234
	AuCu ₂₄ H ₂₂ (PPh ₃) ₁₂ , AuCu ₂₄ H ₂₂ ((p-FPh) ₃ P) ₁₂	Direct co-reduction strategy	Cu	24	Kernel surface doping	189
	[Cu ₁₃ Au ₁₂ (PPh ₃) ₁₀ (SR) ₅ Cl ₂] ²⁺ , SR = PhC ₂ H ₄ S	Direct co-reduction strategy	Cu	13	Kernel surface doping	235
(M–Au) ₂₅ series NCs	Au ₂₂ Ir ₃ (PET) ₁₈	Intercluster reaction strategy	Ir	3	Kernel doping	236
	Pd ₂ Au ₂₃ (PPh ₃) ₁₀ Br ₇	Direct co-reduction strategy	Pd	2	Center doping	237
	[Au ₄ Ag ₂₃ (C≡C ^t Bu) ₁₀ (dppf) ₄ Cl ₇](PF ₆) ₂	Direct co-reduction strategy	Ag	23	Kernel surface doping, Motif doping	238
(M–Au) ₂₇ series NCs	Au ₂₅ Ag ₂ (SR) ₁₈ , SR = SC ₂ H ₄ Ph	Direct co-reduction strategy	Ag	2	Motif doping	239
	Ag _{29−x} Au _x (SR) ₁₂ (pph) ₄ , SR = S ₂ C ₆ H ₆ (x = 1–5)	Direct co-reduction strategy	Ag	24–28	Kernel surface doping, Motif doping	240
(M–Au) ₂₉ series NCs	[Au ₅ Ag ₂₄ (C≡CC ₆ H ₄ [−] p ^{−t} Bu) ₁₆ (dppf) ₄ Cl ₄](PF ₆) ₃	Direct co-reduction strategy	Ag	24	Kernel surface doping, Motif doping	238
	Au ₂₄ Cu ₆ (SPh ^t Bu) ₂₂	Intercluster reaction strategy	Cu	6	Motif doping	241
(M–Au) ₃₀ series NCs	[Ag ₃₃ AuS ₂ (SR) ₁₈ (CF ₃ COO) ₉ (DMF) ₆]	Direct co-reduction strategy	Ag	33	Kernel surface doping, Motif doping	242
	[AuAg ₃₃ (BTCA) ₃ (C≡Cbu ^t) ₉ (tfa) ₄ (CH ₃ OH) ₃]SbF ₆	Direct co-reduction strategy	Ag	33	Kernel surface doping, Motif doping	243
(M–Au) ₃₈ series NCs	Au _{38−x} Cu _x (2,4-(CH ₃) ₂ C ₆ H ₃ S) ₂₄ (x = 0–6)	Intercluster reaction strategy	Cu	0–6	Motif doping	244
M ₂ Au ₃₆ series NCs	M ₂ Au ₃₆ (SR) ₂₄ , SR = SC ₂ H ₄ Ph/ SC ₆ H ₁₃	Direct co-reduction strategy	Pd, Pt	2	Center doping	245–248
(M–Au) ₄₀ series NCs	AuAg ₃₉ (TBBM) ₂₁ (CH ₃ COO) ₁₁	Intercluster reaction strategy	Ag	39	Kernel surface doping, Motif doping	249
(M–Au) ₄₁ series NCs	[Au ₃ Ag ₃₈ (SR) ₂₄ X ₅] ^{2−} (X = Cl or Br), SR = SCH ₂ Ph	Direct co-reduction strategy	Ag	38	Kernel surface doping, Motif doping	250
(M–Au) ₄₂ series NCs	Au ₃₈ Cd ₄ (DMBT) ₃₀	Metal-exchange strategy	Cd	4	Kernel surface doping	251
(M–Au) ₄₄ series NCs	Au ₁₂ @S ₈ @Ag ₃₂ (PS) ₂₄] ²⁺	Direct co-reduction strategy	Ag	32	Kernel surface doping	252
	[Au _{12+x} Cu ₃₂ (SR) _{30+x}] ⁴⁺ , SR = SPhCF ₃	Direct co-reduction strategy	Cu	32	Motif doping	253
	Au ₂₄ Ag ₂₀ (2-SPy) ₄ (PhC≡C) ₂₀ Cl ₂	Direct co-reduction strategy	Ag	6	Kernel surface doping	254
	Au ₂ Ag ₄₂ (S-Adm) ₂₇ (BPh ₄)	Direct co-reduction strategy	Ag	42	Kernel surface doping, Motif doping	255



Table 1 (Contd.)

Series NC _s name	NC _s formula	Synthesis method	Structural characteristic			Reference
			Doping type	Doping number	Doping position	
M ₃₂ Au ₁₂ series NCs	[Au ₁₂ Ag ₃₂ (FTP) ₃₀] ⁴⁻	Metal-exchange strategy	Ag	32	Kernel surface doping, Motif doping	256
(M-Au) ₄₅ series NCs	Au ₁₂ Ag ₃₂ (SR) ₃₀ SR = SPhF/SPhF ₂ /SPhCF ₃	Direct co-reduction strategy	Ag	32	Kernel surface doping, Motif doping	190
(M-Au) ₄₅ series NCs	Au ₉ Ag ₃₆ (SR) ₂₇ (PPh ₃) ₆ , SR = SPhCl ₂	Direct co-reduction strategy	Ag	36	Kernel surface doping, Motif doping	257
(M-Au) ₄₈ series NCs	Au ₂₆ Ag ₂₂ (TBBT) ₃₀	Direct co-reduction strategy	Ag	22	Kernel surface doping, Motif doping	258
(M-Au) ₄₉ series NCs	[Au ₁₉ Cu ₃₀ (C=CR) ₂₂ (Ph ₃ P) ₆ Cl ₂](NO ₃) ₃ , RC=C=H ₃ C ₄ S ₃ -C≡CH/PhC≡CH	Direct co-reduction strategy	Cu	30	Kernel surface doping	259
(M-Au) ₅₀ series NCs	[Au ₂ Ag ₄₈ (S ^t Bu) ₂₀ (Dppm) ₆ Br ₁₁]	Direct co-reduction strategy	Ag	48	Kernel surface doping, Motif doping	255
(M-Au) ₆₂ series NCs	Au ₃₄ Ag ₂₈ (PhC≡C) ₃₄	Direct co-reduction strategy	Ag	28	Kernel surface doping	260
(M-Au) ₇₀ series NCs	[Ag ₄₆ Au ₂₄ (S ^t Bu) ₃₂](BPh ₄) ₂	Direct co-reduction strategy	Ag	46	Kernel doping	261
(M-Au) ₁₁₀ series NCs	[Au ₈₀ Ag ₃₀ (C≡CPh) ₄₂ Cl ₉]Cl	Direct co-reduction strategy	Ag	30	Kernel surface doping	262
(M-Au) ₁₂₄ series NCs	Au ₅₇ Ag ₅₃ (C≡CPh) ₄₀ Br ₁₂	Direct co-reduction strategy	Ag	53	All	263
(M-Au) ₁₂₄ series NCs	[Au ₅₂ Cu ₇₂ (<i>p</i> -MBT) ₅₅] ⁺ Cl ⁻ , <i>p</i> -MBT = SPh- <i>p</i> -CH ₃	Direct co-reduction strategy	Cu	72	Kernel doping	264
(M-Au) ₁₃₀ series NCs	Au _{130-x} Ag _x (TBBT) ₅₅	Direct co-reduction strategy	Ag	98	All	265

Ligand abbreviations	Formula
dppy	C ₁₇ H ₁₄ NP
pph	C ₁₈ H ₁₅ P
dppm	C ₂₅ H ₂₂ P ₂
S-Adm	C ₁₀ H ₁₆ S
2,4-DMBT	C ₈ H ₁₀ S
TBM	C ₂₂ H ₁₈
py	C ₅ H ₅ N
TBBT	C ₁₀ H ₁₄ S
S ^t Bu	C ₄ H ₁₀ S
dppf	C ₃₄ H ₂₈ FeP ₂
PET	C ₈ H ₁₀ S
CHM	C ₆ H ₁₂ S
SSR	C ₆ H ₆ S ₂
BTCA	C ₈ H ₁₀ O ₈

Acknowledgements

We acknowledge the financial support of the Natural Science research project of Universities in Anhui Province (KJ2021ZD0001), Natural Science Foundation of Anhui Province (2208085MB20).

Notes and references

- 1 W. Zhang, W. Lai and R. Cao, *Chem. Rev.*, 2017, **117**, 3717–3797.

- 2 H. Lei, X. Li, J. Meng, H. Zheng, W. Zhang and R. Cao, *ACS Catal.*, 2019, **9**, 4320–4344.
- 3 F. Li, G.-F. Han and J.-B. Baek, *Acc. Chem. Res.*, 2022, **55**, 110–120.
- 4 R. Zheng, Z. Liu, Y. Wang, Z. Xie and M. He, *Joule*, 2022, **6**, 1148–1159.
- 5 Y. Jiang, H. Fu, Z. Liang, Q. Zhang and Y. Du, *Chem. Soc. Rev.*, 2024, **53**, 714–763.
- 6 J. Zhu, L. Hu, P. Zhao, L. Y. S. Lee and K.-Y. Wong, *Chem. Rev.*, 2020, **120**, 851–918.
- 7 Y. Jiao, Y. Zheng, M. Jaroniec and S. Z. Qiao, *Chem. Soc. Rev.*, 2015, **44**, 2060–2086.
- 8 T. E. Jones, D. Teschner and S. Piccinin, *Chem. Rev.*, 2024, **124**, 9136–9223.
- 9 H. Ding, H. Liu, W. Chu, C. Wu and Y. Xie, *Chem. Rev.*, 2021, **121**, 13174–13212.
- 10 H. Li, Y. Lin, J. Duan, Q. Wen, Y. Liu and T. Zhai, *Chem. Soc. Rev.*, 2024, **53**, 10709–10740.
- 11 J. Park, T. Kwon, J. Kim, H. Jin, H. Y. Kim, B. Kim, S. H. Joo and K. Lee, *Chem. Soc. Rev.*, 2018, **47**, 8173–8202.
- 12 C. Hu, R. Paul, Q. Dai and L. Dai, *Chem. Soc. Rev.*, 2021, **50**, 11785–11843.
- 13 X. Yan, Y. Jia and X. Yao, *Chem. Soc. Rev.*, 2018, **47**, 7628–7658.
- 14 P.-P. Yang and M.-R. Gao, *Chem. Soc. Rev.*, 2023, **52**, 4343–4380.



- 15 L. Li, X. Li, Y. Sun and Y. Xie, *Chem. Soc. Rev.*, 2022, **51**, 1234–1252.
- 16 W. Ma, X. He, W. Wang, S. Xie, Q. Zhang and Y. Wang, *Chem. Soc. Rev.*, 2021, **50**, 12897–12914.
- 17 C. Wang, Z. Lv, W. Yang, X. Feng and B. Wang, *Chem. Soc. Rev.*, 2023, **52**, 1382–1427.
- 18 G. Qing, R. Ghazfar, S. T. Jackowski, F. Habibzadeh, M. M. Ashtiani, C.-P. Chen, M. R. Smith III and T. W. Hamann, *Chem. Rev.*, 2020, **120**, 5437–5516.
- 19 C. Tang and S.-Z. Qiao, *Chem. Soc. Rev.*, 2019, **48**, 3166–3180.
- 20 H. Xu, Y. Ma, J. Chen, W.-x. Zhang and J. Yang, *Chem. Soc. Rev.*, 2022, **51**, 2710–2758.
- 21 W. Guo, K. Zhang, Z. Liang, R. Zou and Q. Xu, *Chem. Soc. Rev.*, 2019, **48**, 5658–5716.
- 22 X. Sun, R. B. Araujo, E. C. dos Santos, Y. Sang, H. Liu and X. Yu, *Chem. Soc. Rev.*, 2024, **53**, 7392–7425.
- 23 C. Wei, S. Sun, D. Mandler, X. Wang, S. Z. Qiao and Z. J. Xu, *Chem. Soc. Rev.*, 2019, **48**, 2518–2534.
- 24 D.-H. Yang, Y. Tao, X. Ding and B.-H. Han, *Chem. Soc. Rev.*, 2022, **51**, 761–791.
- 25 S. Ji, Y. Chen, X. Wang, Z. Zhang, D. Wang and Y. Li, *Chem. Rev.*, 2020, **120**, 11900–11955.
- 26 R. Lang, X. Du, Y. Huang, X. Jiang, Q. Zhang, Y. Guo, K. Liu, B. Qiao, A. Wang and T. Zhang, *Chem. Rev.*, 2020, **120**, 11986–12043.
- 27 C. Gao, J. Low, R. Long, T. Kong, J. Zhu and Y. Xiong, *Chem. Rev.*, 2020, **120**, 12175–12216.
- 28 A. Wang, J. Li and T. Zhang, *Nat. Rev. Chem.*, 2018, **2**, 65–81.
- 29 Y. Wang, H. Su, Y. He, L. Li, S. Zhu, H. Shen, P. Xie, X. Fu, G. Zhou, C. Feng, D. Zhao, F. Xiao, X. Zhu, Y. Zeng, M. Shao, S. Chen, G. Wu, J. Zeng and C. Wang, *Chem. Rev.*, 2020, **120**, 12217–12314.
- 30 Q. Yao, M. Zhu, Z. Yang, X. Song, X. Yuan, Z. Zhang, W. Hu and J. Xie, *Nat. Rev. Mater.*, 2025, **10**, 89–108.
- 31 S. Maity, S. Kolay, S. Chakraborty, A. Devi, Rashmi and A. Patra, *Chem. Soc. Rev.*, 2025, **54**, 1785–1844.
- 32 C. Dong, Y. Li, D. Cheng, M. Zhang, J. Liu, Y.-G. Wang, D. Xiao and D. Ma, *ACS Catal.*, 2020, **10**, 11011–11045.
- 33 J. Shi, *Chem. Rev.*, 2013, **113**, 2139–2181.
- 34 Y. Li, Y. Li, H. Sun, L. Gao, X. Jin, Y. Li, Z. Lv, L. Xu, W. Liu and X. Sun, *Nano-Micro Lett.*, 2024, **16**, 139.
- 35 C. S. Day, R. J. Somerville and R. Martin, *Nat. Catal.*, 2021, **4**, 124–133.
- 36 R. Jin, C. Zeng, M. Zhou and Y. Chen, *Chem. Rev.*, 2016, **116**, 10346–10413.
- 37 Q. Yao, T. Chen, X. Yuan and J. Xie, *Acc. Chem. Res.*, 2018, **51**, 1338–1348.
- 38 I. Chakraborty and T. Pradeep, *Chem. Rev.*, 2017, **117**, 8208–8271.
- 39 Q. Yao, Z. Wu, Z. Liu, Y. Lin, X. Yuan and J. Xie, *Chem. Sci.*, 2021, **12**, 99–127.
- 40 L. Liu and A. Corma, *Chem. Rev.*, 2018, **118**, 4981–5079.
- 41 Q. Tang, G. Hu, V. Fung and D.-e. Jiang, *Acc. Chem. Res.*, 2018, **51**, 2793–2802.
- 42 Y. Guo, M. Wang, Q. Zhu, D. Xiao and D. Ma, *Nat. Catal.*, 2022, **5**, 766–776.
- 43 L. Liu and A. Corma, *Chem. Rev.*, 2023, **123**, 4855–4933.
- 44 C.-C. Hou, H.-F. Wang, C. Li and Q. Xu, *Energy Environ. Sci.*, 2020, **13**, 1658–1693.
- 45 H. Shen, Q. Wu, M. S. Asre Hazer, X. Tang, Y.-Z. Han, R. Qin, C. Ma, S. Malola, B. K. Teo, H. Häkkinen and N. Zheng, *Chem*, 2022, **8**, 2380–2392.
- 46 X. Cai, G. Saranya, K. Shen, M. Chen, R. Si, W. Ding and Y. Zhu, *Angew. Chem., Int. Ed.*, 2019, **58**, 9964–9968.
- 47 C. Dong, R.-W. Huang, A. Sagadevan, P. Yuan, L. Gutiérrez-Arzaluz, A. Ghosh, S. Nematulloev, B. Alamer, O. F. Mohammed, I. Hussain, M. Rueping and O. M. Bakr, *Angew. Chem., Int. Ed.*, 2023, **62**, e202307140.
- 48 Y. Du, H. Sheng, D. Astruc and M. Zhu, *Chem. Rev.*, 2020, **120**, 526–622.
- 49 X. Cai, H. Wang, Y. Tian, W. Ding and Y. Zhu, *ACS Catal.*, 2024, **14**, 11918–11930.
- 50 G. J. Hutchings, *J. Catal.*, 1985, **96**, 292–295.
- 51 M. Sankar, Q. He, R. V. Engel, M. A. Sainna, A. J. Logsdail, A. Roldan, D. J. Willock, N. Agarwal, C. J. Kiely and G. J. Hutchings, *Chem. Rev.*, 2020, **120**, 3890–3938.
- 52 Z.-J. Guan, J.-J. Li, F. Hu and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202209725.
- 53 T. Higaki, Y. Li, S. Zhao, Q. Li, S. Li, X.-S. Du, S. Yang, J. Chai and R. Jin, *Angew. Chem., Int. Ed.*, 2019, **58**, 8291–8302.
- 54 J. Zhao and R. Jin, *Nano Today*, 2018, **18**, 86–102.
- 55 X. Du and R. Jin, *ACS Nano*, 2019, **13**, 7383–7387.
- 56 X.-K. Wan, J.-Q. Wang, Z.-A. Nan and Q.-M. Wang, *Sci. Adv.*, **3**, e1701823.
- 57 Q. Shi, Z. Qin, S. Sharma and G. Li, *Chem. Rec.*, 2021, **21**, 879–892.
- 58 X. Cai, G. Li, W. Hu and Y. Zhu, *ACS Catal.*, 2022, **12**, 10638–10653.
- 59 K. Xiao, Y. Xue, B. Yang and L. Zhao, *CCS Chem.*, 2021, **3**, 555–565.
- 60 W.-D. Tian, W.-D. Si, S. Havenridge, C. Zhang, Z. Wang, C. M. Aikens, C.-H. Tung and D. Sun, *Sci. Bull.*, 2024, **69**, 40–48.
- 61 W.-D. Si, Y.-Z. Li, S.-S. Zhang, S. Wang, L. Feng, Z.-Y. Gao, C.-H. Tung and D. Sun, *ACS Nano*, 2021, **15**, 16019–16029.
- 62 W. D. Si, C. Zhang, M. Zhou, Z. Wang, L. Feng, C. H. Tung and D. Sun, *Sci. Adv.*, 2024, **10**, eadm6928.
- 63 W. Si, C. Zhang, M. Zhou, W. Tian, Z. Wang, Q. Hu, K. Song, L. Feng, X. Q. Huang and Z. Y. Gao, *Sci. Adv.*, 2023, **9**, eadg3587.
- 64 X. Kang, H. Chong and M. Zhu, *Nanoscale*, 2018, **10**, 10758–10834.
- 65 R. Jin, G. Li, S. Sharma, Y. Li and X. Du, *Chem. Rev.*, 2021, **121**, 567–648.
- 66 H. Yan, H. Xiang, J. Liu, R. Cheng, Y. Ye, Y. Han and C. Yao, *Small*, 2022, **18**, 2200812.
- 67 X. Liu, X. Cai and Y. Zhu, *Acc. Chem. Res.*, 2023, **56**, 1528–1538.
- 68 G. X. Pei, L. Zhang and X. Sun, *Coord. Chem. Rev.*, 2024, **506**, 215692.



- 69 X. Kang, Y. Li, M. Zhu and R. Jin, *Chem. Soc. Rev.*, 2020, **49**, 6443–6514.
- 70 M. Zhu, E. Lanni, N. Garg, M. E. Bier and R. Jin, *J. Am. Chem. Soc.*, 2008, **130**, 1138–1139.
- 71 J. Fang, B. Zhang, Q. Yao, Y. Yang, J. Xie and N. Yan, *Coord. Chem. Rev.*, 2016, **322**, 1–29.
- 72 Y. Negishi, T. Iwai and M. Ide, *Chem. Commun.*, 2010, **46**, 4713–4715.
- 73 J.-P. Choi, C. A. Fields-Zinna, R. L. Stiles, R. Balasubramanian, A. D. Douglas, M. C. Crowe and R. W. Murray, *J. Phys. Chem. C*, 2010, **114**, 15890–15896.
- 74 Z. Gan, N. Xia and Z. Wu, *Acc. Chem. Res.*, 2018, **51**, 2774–2783.
- 75 Z. Wu, *Angew. Chem., Int. Ed.*, 2012, **51**, 2934–2938.
- 76 N. Xia and Z. Wu, *J. Mater. Chem. C*, 2016, **4**, 4125–4128.
- 77 S. Wang, Q. Li, X. Kang and M. Zhu, *Acc. Chem. Res.*, 2018, **51**, 2784–2792.
- 78 S. Wang, Y. Song, S. Jin, X. Liu, J. Zhang, Y. Pei, X. Meng, M. Chen, P. Li and M. Zhu, *J. Am. Chem. Soc.*, 2015, **137**, 4018–4021.
- 79 K. R. Krishnadas, A. Ghosh, A. Bakshi, I. Chakraborty, G. Natarajan and T. Pradeep, *J. Am. Chem. Soc.*, 2016, **138**, 140–148.
- 80 X. Zhu, L. Chen, Y. Liu and Z. Tang, *Polyoxometalates*, 2023, **2**, 9140031.
- 81 Q. Pang, X. Fan, K. Sun, K. Xiang, L. Dong, S. Zhao, Y. D. Kim, B. Li, Q. Liu, Z. Liu and Z. Peng, *J. Mater. Chem. A*, 2023, **11**, 14451–14468.
- 82 S. Lu and T. Zhang, *Chem Catal.*, 2022, **2**, 1505–1509.
- 83 H. Li and G. Li, *J. Mater. Chem. A*, 2023, **11**, 9383–9400.
- 84 Z. W. Seh, J. Kibsgaard, C. F. Dickens, I. Chorkendorff, J. K. Nørskov and T. F. Jaramillo, *Science*, 2017, **355**, eaad4998.
- 85 K. Motegi, T. Nakajima, K. Hirao and L. Seijo, *J. Chem. Phys.*, 2001, **114**, 6000–6006.
- 86 D. V. Dao, T. T. D. Nguyen, P. Uthirakumar, Y.-H. Cho, G.-C. Kim, J.-K. Yang, D.-T. Tran, T. D. Le, H. Choi, H. Y. Kim, Y.-T. Yu and I.-H. Lee, *Appl. Catal., B*, 2021, **286**, 119947.
- 87 K. Kwak, W. Choi, Q. Tang, M. Kim, Y. Lee, D.-e. Jiang and D. Lee, *Nat. Commun.*, 2017, **8**, 14723.
- 88 M. A. Tofanelli and C. J. Ackerson, *J. Am. Chem. Soc.*, 2012, **134**, 16937–16940.
- 89 M. Walter, J. Akola, O. Lopez-Acevedo, P. D. Jadzinsky, G. Calero, C. J. Ackerson, R. L. Whetten, H. Grönbeck and H. Häkkinen, *Proc. Natl. Acad. Sci. U.S.A.*, 2008, **105**, 9157–9162.
- 90 K. Kwak, Q. Tang, M. Kim, D.-e. Jiang and D. Lee, *J. Am. Chem. Soc.*, 2015, **137**, 10833–10840.
- 91 S. C. Marinescu, J. R. Winkler and H. B. Gray, *Proc. Natl. Acad. Sci. U.S.A.*, 2012, **109**, 15127–15131.
- 92 G. A. N. Felton, R. S. Glass, D. L. Lichtenberger and D. H. Evans, *Inorg. Chem.*, 2006, **45**, 9181–9184.
- 93 W. Lubitz, H. Ogata, O. Rüdiger and E. Reijerse, *Chem. Rev.*, 2014, **114**, 4081–4148.
- 94 F. A. Armstrong and G. S. Wilson, *Electrochim. Acta*, 2000, **45**, 2623–2645.
- 95 S. S. Kumar, K. Kwak and D. Lee, *Anal. Chem.*, 2011, **83**, 3244–3247.
- 96 M. L. Helm, M. P. Stewart, R. M. Bullock, M. R. DuBois and D. L. DuBois, *Science*, 2011, **333**, 863–866.
- 97 P. Zhang, M. Wang, Y. Yang, T. Yao and L. Sun, *Angew. Chem., Int. Ed.*, 2014, **53**, 13803–13807.
- 98 X. Hu, B. S. Brunschwig and J. C. Peters, *J. Am. Chem. Soc.*, 2007, **129**, 8988–8998.
- 99 F. Sun, L. Qin, Z. Tang and Q. Tang, *Chem. Sci.*, 2024, **15**, 16142–16155.
- 100 W. Choi, G. Hu, K. Kwak, M. Kim, D.-e. Jiang, J.-P. Choi and D. Lee, *ACS Appl. Mater. Interfaces*, 2018, **10**, 44645–44653.
- 101 M. Sera, S. Hossain, S. Yoshikawa, K. Takemae, A. Ikeda, T. Tanaka, T. Kosaka, Y. Niihori, T. Kawawaki and Y. Negishi, *J. Am. Chem. Soc.*, 2024, **146**, 29684–29693.
- 102 Y. Li, S. Li, A. V. Nagarajan, Z. Liu, S. Nevins, Y. Song, G. Mpourmpakis and R. Jin, *J. Am. Chem. Soc.*, 2021, **143**, 11102–11108.
- 103 Y. Du, J. Xiang, K. Ni, Y. Yun, G. Sun, X. Yuan, H. Sheng, Y. Zhu and M. Zhu, *Inorg. Chem. Front.*, 2018, **5**, 2948–2954.
- 104 A. Devi, H. Minhas, L. Sahoo, Rashi, S. Gratiou, A. Das, S. Mandal, B. Pathak and A. Patra, *Nanoscale*, 2024, **16**, 1758–1769.
- 105 Y.-K. Lv, Y. Han, K. Wang, W.-Y. Sun, C.-X. Du, R.-W. Huang, P. Peng and S.-Q. Zang, *ACS Nano*, 2024, **18**, 32186–32195.
- 106 Y. Du, C. Li, Y. Dai, H. Yin and M. Zhu, *Nanoscale Horiz.*, 2024, **9**, 1262–1278.
- 107 M. S. Bootharaju, C. W. Lee, G. Deng, H. Kim, K. Lee, S. Lee, H. Chang, S. Lee, Y.-E. Sung, J. S. Yoo, N. Zheng and T. Hyeon, *Adv. Mater.*, 2023, **35**, 2207765.
- 108 Y. Liu, Z. Li, X.-H. Liu, N. Pinna and Y. Wang, *Nanoscale Horiz.*, 2023, **8**, 1435–1439.
- 109 W. Kurashige, R. Hayashi, K. Wakamatsu, Y. Kataoka, S. Hossain, A. Iwase, A. Kudo, S. Yamazoe and Y. Negishi, *ACS Appl. Energy Mater.*, 2019, **2**, 4175–4187.
- 110 K. Zhang and R. Zou, *Small*, 2021, **17**, 2100129.
- 111 Y.-C. Zhang, C. Han, J. Gao, L. Pan, J. Wu, X.-D. Zhu and J.-J. Zou, *ACS Catal.*, 2021, **11**, 12485–12509.
- 112 X. Liu, Y. Tang, L. Chen, L. Wang, Y. Liu and Z. Tang, *Int. J. Hydrogen Energy*, 2024, **53**, 300–307.
- 113 Y. Sun, J. Luo, M. Zhang, J. Li, J. Yu, S. Lu, W. Song, Y. Wei, Z. Li and J. Liu, *ACS Appl. Mater. Interfaces*, 2023, **15**, 10696–10708.
- 114 P. Su, B. Tang and F.-X. Xiao, *Small*, 2024, **20**, 2307619.
- 115 Z. Ma, Z. P. Cano, A. Yu, Z. Chen, G. Jiang, X. Fu, L. Yang, T. Wu, Z. Bai and J. Lu, *Angew. Chem., Int. Ed.*, 2020, **59**, 18334–18348.
- 116 Y. Yuan, Q. Zhang, L. Yang, L. Wang, W. Shi, P. Liu, R. Gao, L. Zheng, Z. Chen and Z. Bai, *Adv. Funct. Mater.*, 2022, **32**, 2206081.
- 117 S. Siahrostami, A. Verdaguer-Casadevall, M. Karamad, D. Deiana, P. Malacrida, B. Wickman, M. Escudero-Escribano, E. A. Paoli, R. Frydendal, T. W. Hansen,



- I. Chorkendorff, I. E. L. Stephens and J. Rossmeisl, *Nat. Mater.*, 2013, **12**, 1137–1143.
- 118 T. Murayama and I. Yamanaka, *J. Phys. Chem. C*, 2011, **115**, 5792–5799.
- 119 Q. Chang, P. Zhang, A. H. B. Mostaghimi, X. Zhao, S. R. Denny, J. H. Lee, H. Gao, Y. Zhang, H. L. Xin, S. Siahrostami, J. G. Chen and Z. Chen, *Nat. Commun.*, 2020, **11**, 2178.
- 120 J. A. van Bokhoven and J. T. Miller, *J. Phys. Chem. C*, 2007, **111**, 9245–9249.
- 121 N. S. Phala and E. Van Steen, *Gold Bull.*, 2007, **40**, 150–153.
- 122 W. Chen and S. Chen, *Angew. Chem., Int. Ed.*, 2009, **48**, 4386–4389.
- 123 L. Wang, Z. Tang, W. Yan, H. Yang, Q. Wang and S. Chen, *ACS Appl. Mater. Interfaces*, 2016, **8**, 20635–20641.
- 124 X. Zou, S. He, X. Kang, S. Chen, H. Yu, S. Jin, D. Astruc and M. Zhu, *Chem. Sci.*, 2021, **12**, 3660–3667.
- 125 L. Xu, Q. Li, T. Li, J. Chai, S. Yang and M. Zhu, *Inorg. Chem. Front.*, 2021, **8**, 4820–4827.
- 126 W. Yan, Z. Tang, L. Wang, Q. Wang, H. Yang and S. Chen, *Int. J. Hydrogen Energy*, 2017, **42**, 218–227.
- 127 B. Kumar, T. Kawawaki, N. Shimizu, Y. Imai, D. Suzuki, S. Hossain, L. V. Nair and Y. Negishi, *Nanoscale*, 2020, **12**, 9969–9979.
- 128 J. Wang, B. Zhang, W. Guo, L. Wang, J. Chen, H. Pan and W. Sun, *Adv. Mater.*, 2023, **35**, 2211099.
- 129 Y. Zuo, W. Sheng, W. Tao and Z. Li, *J. Mater. Sci. Technol.*, 2022, **114**, 29–41.
- 130 M. A. Ud Din, M. Idrees, S. Jamil, S. Irfan, G. Nazir, M. A. Mudassir, M. S. Saleem, S. Batool, N. Cheng and R. Saidur, *J. Energy Chem.*, 2023, **77**, 499–513.
- 131 T. Yang, S. Hou, J. Xing, C. Liu, J. Ge and W. Xing, *Nano Res.*, 2023, **16**, 3607–3621.
- 132 A. Han, Z. Zhang, J. Yang, D. Wang and Y. Li, *Small*, 2021, **17**, 2004500.
- 133 J. Bai, D. Liu, J. Yang and Y. Chen, *ChemSusChem*, 2019, **12**, 2117–2132.
- 134 J. Chang, G. Wang, X. Chang, Z. Yang, H. Wang, B. Li, W. Zhang, L. Kovarik, Y. Du, N. Orlovskaya, B. Xu, G. Wang and Y. Yang, *Nat. Commun.*, 2023, **14**, 1346.
- 135 J. Chang, G. Wang, C. Li, Y. He, Y. Zhu, W. Zhang, M. Sajid, A. Kara, M. Gu and Y. Yang, *Joule*, 2023, **7**, 587–602.
- 136 S. Tang, H. Liu, T. Song, X. Cai, X. Liu, W. Ding and Y. Zhu, *Catal. Sci. Technol.*, 2023, **13**, 5821–5824.
- 137 L. Y. Zhang, Y. Gong, H. Liu, W. Yuan and Z. Liu, *Electrochem. Commun.*, 2017, **84**, 1–5.
- 138 Y. Cui, M. Zhao, Y. Zou, J. Zhang, J. Han, Z. Wang and Q. Jiang, *J. Energy Chem.*, 2022, **68**, 556–563.
- 139 J. Li, *Natl. Sci. Rev.*, 2020, **7**, 1762.
- 140 Y. Zhou, Y. Yang, X. Zhu, T. Zhang, D.-d. Ye, R. Chen and Q. Liao, *Adv. Funct. Mater.*, 2022, **32**, 2201872.
- 141 Y. Lu, C. Zhang, X. Li, A. R. Frojd, W. Xing, A. Z. Clayborne and W. Chen, *Nano Energy*, 2018, **50**, 316–322.
- 142 Y. Y. Birdja, E. Pérez-Gallent, M. C. Figueiredo, A. J. Göttle, F. Calle-Vallejo and M. T. M. Koper, *Nat. Energy*, 2019, **4**, 732–745.
- 143 A. D. Handoko, F. Wei, Jenndy, B. S. Yeo and Z. W. Seh, *Nat. Catal.*, 2018, **1**, 922–934.
- 144 M. B. Ross, P. De Luna, Y. Li, C.-T. Dinh, D. Kim, P. Yang and E. H. Sargent, *Nat. Catal.*, 2019, **2**, 648–658.
- 145 S. Nitopi, E. Bertheussen, S. B. Scott, X. Liu, A. K. Engstfeld, S. Horch, B. Seger, I. E. L. Stephens, K. Chan, C. Hahn, J. K. Nørskov, T. F. Jaramillo and I. Chorkendorff, *Chem. Rev.*, 2019, **119**, 7610–7672.
- 146 L. Wang, W. Chen, D. Zhang, Y. Du, R. Amal, S. Qiao, J. Wu and Z. Yin, *Chem. Soc. Rev.*, 2019, **48**, 5310–5349.
- 147 S. Jin, Z. Hao, K. Zhang, Z. Yan and J. Chen, *Angew. Chem., Int. Ed.*, 2021, **60**, 20627–20648.
- 148 S. Zhuang, D. Chen, L. Liao, Y. Zhao, N. Xia, W. Zhang, C. Wang, J. Yang and Z. Wu, *Angew. Chem., Int. Ed.*, 2020, **59**, 3073–3077.
- 149 S. Li, A. V. Nagarajan, D. R. Alfonso, M. Sun, D. R. Kauffman, G. Mpourmpakis and R. Jin, *Angew. Chem., Int. Ed.*, 2021, **60**, 6351–6356.
- 150 Y. Sun, X. Liu, K. Xiao, Y. Zhu and M. Chen, *ACS Catal.*, 2021, **11**, 11551–11560.
- 151 S. Li, D. Alfonso, A. V. Nagarajan, S. D. House, J. C. Yang, D. R. Kauffman, G. Mpourmpakis and R. Jin, *ACS Catal.*, 2020, **10**, 12011–12016.
- 152 S. Zhuang, D. Chen, W. Fan, J. Yuan, L. Liao, Y. Zhao, J. Li, H. Deng, J. Yang, J. Yang and Z. Wu, *Nano Lett.*, 2022, **22**, 7144–7150.
- 153 X. Cai, X. Sui, J. Xu, A. Tang, X. Liu, M. Chen and Y. Zhu, *CCS Chem.*, 2021, **3**, 408–420.
- 154 H. Seong, M. Choi, S. Park, H.-w. Kim, J. Kim, W. Kim, J. S. Yoo and D. Lee, *ACS Energy Lett.*, 2022, **7**, 4177–4184.
- 155 X. Lin, W. Ma, K. Sun, B. Sun, X. Fu, X. Ren, C. Liu and J. Huang, *J. Phys. Chem. Lett.*, 2021, **12**, 552–557.
- 156 Y. Li, G. J. Stec, A. E. Thorarinsdottir, R. D. McGillicuddy, S.-L. Zheng and J. A. Mason, *Chem. Sci.*, 2023, **14**, 12283–12291.
- 157 J. Xu, L. Xiong, X. Cai, S. Tang, A. Tang, X. Liu, Y. Pei and Y. Zhu, *Chem. Sci.*, 2022, **13**, 2778–2782.
- 158 G. Deng, H. Yun, M. S. Bootharaju, F. Sun, K. Lee, X. Liu, S. Yoo, Q. Tang, Y. J. Hwang and T. Hyeon, *J. Am. Chem. Soc.*, 2023, **145**, 27407–27414.
- 159 M. Ding, L. Tang, X. Ma, C. Song and S. Wang, *Commun. Chem.*, 2022, **5**, 172.
- 160 S. Su, Y. Zhou, L. Xiong, S. Jin, Y. Du and M. Zhu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202404629.
- 161 H. Seong, Y. Jo, V. Efremov, Y. Kim, S. Park, S. M. Han, K. Chang, J. Park, W. Choi, W. Kim, C. H. Choi, J. S. Yoo and D. Lee, *J. Am. Chem. Soc.*, 2023, **145**, 2152–2160.
- 162 Y. Wu, Q. Hu, Q. Chen, X. Jiao and Y. Xie, *Acc. Chem. Res.*, 2023, **56**, 2500–2513.
- 163 H. Li, J. Zhao, L. Luo, J. Du and J. Zeng, *Acc. Chem. Res.*, 2021, **54**, 1454–1464.
- 164 L. Huang, R. Lu, W. Zhang, Y. Fan, Y. Du, K. Ni, Y. Zhu and M. Zhu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202412964.
- 165 Y. Du, P. Wang, Y. Fang and M. Zhu, *ChemSusChem*, 2024, e202402085.



- 166 Y. Tan, G. Sun, T. Jiang, D. Liu, Q. Li, S. Yang, J. Chai, S. Gao, H. Yu and M. Zhu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202317471.
- 167 X. Liu, E. Wang, M. Zhou, Y. Wan, Y. Zhang, H. Liu, Y. Zhao, J. Li, Y. Gao and Y. Zhu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202207685.
- 168 Y.-M. Wang, F.-Q. Yan, Q.-Y. Wang, C.-X. Du, L.-Y. Wang, B. Li, S. Wang and S.-Q. Zang, *Nat. Commun.*, 2024, **15**, 1843.
- 169 J. Mu, X.-W. Gao, T. Yu, L.-K. Zhao, W.-B. Luo, H. Yang, Z.-M. Liu, Z. Sun, Q.-F. Gu and F. Li, *Adv. Sci.*, 2024, **11**, 2308979.
- 170 H. Liu, L. Bai, A. Bergmann, B. R. Cuenya and J. Luo, *Chem.*, 2024, **10**, 2963–2986.
- 171 Y. Yao, J. Wang, U. B. Shahid, M. Gu, H. Wang, H. Li and M. Shao, *Electrochem. Energy Rev.*, 2020, **3**, 239–270.
- 172 Z. Huang, M. Rafiq, A. R. Woldu, Q.-X. Tong, D. Astruc and L. Hu, *Coord. Chem. Rev.*, 2023, **478**, 214981.
- 173 Š. Kment, A. Bakandritsos, I. Tantis, H. Kmentová, Y. Zuo, O. Henrotte, A. Naldoni, M. Otyepka, R. S. Varma and R. Zbořil, *Chem. Rev.*, 2024, **124**, 11767–11847.
- 174 Y. Shi, Z. Zhao, D. Yang, J. Tan, X. Xin, Y. Liu and Z. Jiang, *Chem. Soc. Rev.*, 2023, **52**, 6938–6956.
- 175 L. Collado, A. H. Pizarro, M. Barawi, M. Garcia-Tecedor, M. Liras and V. A. de la Pena O'Shea, *Chem. Soc. Rev.*, 2024, **53**, 11334–11389.
- 176 C. Yao, N. Guo, S. Xi, C.-Q. Xu, W. Liu, X. Zhao, J. Li, H. Fang, J. Su, Z. Chen, H. Yan, Z. Qiu, P. Lyu, C. Chen, H. Xu, X. Peng, X. Li, B. Liu, C. Su, S. J. Pennycook, C.-J. Sun, J. Li, C. Zhang, Y. Du and J. Lu, *Nat. Commun.*, 2020, **11**, 4389.
- 177 M. Han, M. Guo, Y. Yun, Y. Xu, H. Sheng, Y. Chen, Y. Du, K. Ni, Y. Zhu and M. Zhu, *Adv. Funct. Mater.*, 2022, **32**, 2202820.
- 178 Y.-M. Wang, J. Cai, Q.-Y. Wang, Y. Li, Z. Han, S. Li, C.-H. Gong, S. Wang, S.-Q. Zang and T. C. W. Mak, *Angew. Chem., Int. Ed.*, 2022, **61**, e202114538.
- 179 D. P. Butcher and A. A. Gewirth, *Nano Energy*, 2016, **29**, 457–465.
- 180 D. Reyter, D. Bélanger and L. Roué, *Electrochim. Acta*, 2008, **53**, 5977–5984.
- 181 S. Tang, T. Song, X. Cai, W. Ding and Y. Zhu, *Chem. Commun.*, 2024, **60**, 7785–7788.
- 182 Y. Sun, W. Pei, M. Xie, S. Xu, S. Zhou, J. Zhao, K. Xiao and Y. Zhu, *Chem. Sci.*, 2020, **11**, 2440–2447.
- 183 J.-T. Ren, L. Chen, H.-Y. Wang and Z.-Y. Yuan, *Chem. Soc. Rev.*, 2023, **52**, 8319–8373.
- 184 E. P. George, D. Raabe and R. O. Ritchie, *Nat. Rev. Mater.*, 2019, **4**, 515–534.
- 185 M. Suvarna and J. Pérez-Ramírez, *Nat. Catal.*, 2024, **7**, 624–635.
- 186 J. Benavides-Hernández and F. Dumeignil, *ACS Catal.*, 2024, **14**, 11749–11779.
- 187 J. K. Emmanuel, *Bull. Natl. Res.*, 2024, **48**, 24.
- 188 G.-G. Luo, Z.-H. Pan, B.-L. Han, G.-L. Dong, C.-L. Deng, M. Azam, Y.-W. Tao, J. He, C.-F. Sun and D. Sun, *Angew. Chem., Int. Ed.*, 2023, **62**, e202306849.
- 189 A. Chen, X. Kang, S. Jin, W. Du, S. Wang and M. Zhu, *J. Phys. Chem. Lett.*, 2019, **10**, 6124–6128.
- 190 H. Yang, Y. Wang, H. Huang, L. Gell, L. Lehtovaara, S. Malola, H. Häkkinen and N. Zheng, *Nat. Commun.*, 2013, **4**, 2422.
- 191 R.-L. He, F. Hu, Z.-J. Guan and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2024, **63**, e202410827.
- 192 B. Cao, F.-Z. Li and J. Gu, *ACS Catal.*, 2022, **12**, 9735–9752.
- 193 H. Q. Fu, M. Zhou, P. F. Liu, P. Liu, H. Yin, K. Z. Sun, H. G. Yang, M. Al-Mamun, P. Hu, H.-F. Wang and H. Zhao, *J. Am. Chem. Soc.*, 2022, **144**, 6028–6039.
- 194 Y. Chen, C. Zhen, Y. Chen, H. Zhao, Y. Wang, Z. Yue, Q. Wang, J. Li, M. D. Gu, Q. Cheng and H. Yang, *Angew. Chem., Int. Ed.*, 2024, **63**, e202407163.
- 195 S. Yan, C. Peng, C. Yang, Y. Chen, J. Zhang, A. Guan, X. Lv, H. Wang, Z. Wang, T.-K. Sham, Q. Han and G. Zheng, *Angew. Chem., Int. Ed.*, 2021, **60**, 25741–25745.
- 196 J. Ni, C. Zhong, L. Li, M. Su, X. Wang, J. Sun, S. Chen, C. Duan, C. Han and H. Xu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202213826.
- 197 C.-B. Tao, J.-Q. Fan, W. Fei, Y. Zhao and M.-B. Li, *Nanoscale*, 2023, **15**, 109–113.
- 198 Y. Hua, J.-H. Huang, Z.-H. Shao, X.-M. Luo, Z.-Y. Wang, J.-Q. Liu, X. Zhao, X. Chen and S.-Q. Zang, *Adv. Mater.*, 2022, **34**, 2203734.
- 199 Y. Fang, K. Bao, P. Zhang, H. Sheng, Y. Yun, S.-X. Hu, D. Astruc and M. Zhu, *J. Am. Chem. Soc.*, 2021, **143**, 1768–1772.
- 200 H. Xiang, H. Yan, J. Liu, R. Cheng, C.-Q. Xu, J. Li and C. Yao, *J. Am. Chem. Soc.*, 2022, **144**, 14248–14257.
- 201 W. Yu, D. Hu, L. Xiong, Y. Li, X. Kang, S. Chen, S. Wang, Y. Pei and M. Zhu, *Part. Part. Syst. Char.*, 2019, **36**, 1800494.
- 202 Y. Yang, X.-L. Pei and Q.-M. Wang, *J. Am. Chem. Soc.*, 2013, **135**, 16184–16191.
- 203 M. Chen, Z. Lei, W. Feng, C. Li, Q.-M. Wang and F. Li, *Biomaterials*, 2013, **34**, 4284–4295.
- 204 X. Kang, S. Wang, Y. Song, S. Jin, G. Sun, H. Yu and M. Zhu, *Angew. Chem., Int. Ed.*, 2016, **55**, 3611–3614.
- 205 X. Kang, X. Li, H. Yu, Y. Lv, G. Sun, Y. Li, S. Wang and M. Zhu, *RSC Adv.*, 2017, **7**, 28606–28609.
- 206 S. Yamazoe, S. Matsuo, S. Muramatsu, S. Takano, K. Nitta and T. Tsukuda, *Inorg. Chem.*, 2017, **56**, 8319–8325.
- 207 S. Jin, W. Liu, D. Hu, X. Zou, X. Kang, W. Du, S. Chen, S. Wei, S. Wang and M. Zhu, *Chem.-Eur. J.*, 2018, **24**, 3712–3715.
- 208 S. Takano, H. Hirai, S. Muramatsu and T. Tsukuda, *J. Am. Chem. Soc.*, 2018, **140**, 12314–12317.
- 209 Z. Lei, Z.-J. Guan, X.-L. Pei, S.-F. Yuan, X.-K. Wan, J.-Y. Zhang and Q.-M. Wang, *Chem.-Eur. J.*, 2016, **22**, 11156–11160.
- 210 H. Wu, Y.-G. Fang, R. Anumula, G. N. Andrew, G. Cui, W. Fang, Z. Luo and J. Yao, *Nanoscale*, 2021, **13**, 5300–5306.
- 211 A. Tang, X. Cai, Y. Liu, J. Hou, X. Liu, M. Chen and Y. Zhu, *Aggregate*, 2023, **4**, e304.



- 212 R. P. B. Silalahi, Q. Wang, J.-H. Liao, T.-H. Chiu, Y.-Y. Wu, X. Wang, S. Kahlal, J.-Y. Saillard and C. W. Liu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202113266.
- 213 L. Huang, X. Liu, J. Zhou, H.-h. Zou and D. Wen, *Inorg. Chem.*, 2021, **60**, 14–18.
- 214 X. Ma, L. Xiong, L. Qin, Y. Tang, G. Ma, Y. Pei and Z. Tang, *Chem. Sci.*, 2021, **12**, 12819–12826.
- 215 Z.-R. Wen, Z.-J. Guan, Y. Zhang, Y.-M. Lin and Q.-M. Wang, *Chem. Commun.*, 2019, **55**, 12992–12995.
- 216 H. Yang, Y. Wang, J. Lei, L. Shi, X. Wu, V. Mäkinen, S. Lin, Z. Tang, J. He, H. Häkkinen, L. Zheng and N. Zheng, *J. Am. Chem. Soc.*, 2013, **135**, 9568–9571.
- 217 Y. Song, Y. Lv, M. Zhou, T.-Y. Luo, S. Zhao, N. L. Rosi, H. Yu, M. Zhu and R. Jin, *Nanoscale*, 2018, **10**, 12093–12099.
- 218 G. Deng, S. Malola, J. Yan, Y. Han, P. Yuan, C. Zhao, X. Yuan, S. Lin, Z. Tang, B. K. Teo, H. Häkkinen and N. Zheng, *Angew. Chem., Int. Ed.*, 2018, **57**, 3421–3425.
- 219 X. Kang, L. Xiong, S. Wang, Y. Pei and M. Zhu, *Inorg. Chem.*, 2018, **57**, 335–342.
- 220 T. Chen, S. Yang, J. Chai, Y. Song, J. Fan, B. Rao, H. Sheng, H. Yu and M. Zhu, *Sci. Adv.*, 2017, **3**, e1700956.
- 221 B. E. Conn, A. Atnagulov, B. Yoon, R. N. Barnett, U. Landman and T. P. Bigioni, *Sci. Adv.*, 2016, **2**, e1601609.
- 222 J. Xiang, P. Li, Y. Song, X. Liu, H. Chong, S. Jin, Y. Pei, X. Yuan and M. Zhu, *Nanoscale*, 2015, **7**, 18278–18283.
- 223 S. Jin, W. Du, S. Wang, X. Kang, M. Chen, D. Hu, S. Chen, X. Zou, G. Sun and M. Zhu, *Inorg. Chem.*, 2017, **56**, 11151–11159.
- 224 Y. Song, S. Weng, H. Li, H. Yu and M. Zhu, *Inorg. Chem.*, 2019, **58**, 7136–7140.
- 225 Q. Li, K. J. Lambright, M. G. Taylor, K. Kirschbaum, T.-Y. Luo, J. Zhao, G. Mpourmpakis, S. Mokashi-Punekar, N. L. Rosi and R. Jin, *J. Am. Chem. Soc.*, 2017, **139**, 17779–17782.
- 226 S. Jin, F. Xu, W. Du, X. Kang, S. Chen, J. Zhang, X. Li, D. Hu, S. Wang and M. Zhu, *Inorg. Chem.*, 2018, **57**, 5114–5119.
- 227 Y. Li, T.-Y. Luo, M. Zhou, Y. Song, N. L. Rosi and R. Jin, *J. Am. Chem. Soc.*, 2018, **140**, 14235–14243.
- 228 S. Yang, J. Chai, Y. Song, J. Fan, T. Chen, S. Wang, H. Yu, X. Li and M. Zhu, *J. Am. Chem. Soc.*, 2017, **139**, 5668–5671.
- 229 L. V. Nair, S. Hossain, S. Takagi, Y. Imai, G. Hu, S. Wakayama, B. Kumar, W. Kurashige, D.-e. Jiang and Y. Negishi, *Nanoscale*, 2018, **10**, 18969–18979.
- 230 W. Fei, S. Antonello, T. Dainese, A. Dolmella, M. Lahtinen, K. Rissanen, A. Venzo and F. Maran, *J. Am. Chem. Soc.*, 2019, **141**, 16033–16045.
- 231 C. Yao, Y.-j. Lin, J. Yuan, L. Liao, M. Zhu, L.-h. Weng, J. Yang and Z. Wu, *J. Am. Chem. Soc.*, 2015, **137**, 15350–15353.
- 232 Z. Liu, M. Zhou, L. Luo, Y. Wang, E. Kahng and R. Jin, *J. Am. Chem. Soc.*, 2023, **145**, 19969–19981.
- 233 M. S. Bootharaju, C. P. Joshi, M. R. Parida, O. F. Mohammed and O. M. Bakr, *Angew. Chem., Int. Ed.*, 2016, **55**, 922–926.
- 234 Y. Li, M. Zhou, S. Jin, L. Xiong, Q. Yuan, W. Du, Y. Pei, S. Wang and M. Zhu, *Chem. Commun.*, 2019, **55**, 6457–6460.
- 235 S. Yang, J. Chai, T. Chen, B. Rao, Y. Pan, H. Yu and M. Zhu, *Inorg. Chem.*, 2017, **56**, 1771–1774.
- 236 S. Bhat, A. Baksi, S. K. Mudedla, G. Natarajan, V. Subramanian and T. Pradeep, *J. Phys. Chem. Lett.*, 2017, **8**, 2787–2793.
- 237 X. Kang, J. Xiang, Y. Lv, W. Du, H. Yu, S. Wang and M. Zhu, *Chem. Mater.*, 2017, **29**, 6856–6862.
- 238 Y. Du, Z.-J. Guan, Z.-R. Wen, Y.-M. Lin and Q.-M. Wang, *Chem.–Eur. J.*, 2018, **24**, 16029–16035.
- 239 C. Yao, J. Chen, M.-B. Li, L. Liu, J. Yang and Z. Wu, *Nano Lett.*, 2015, **15**, 1281–1287.
- 240 G. Soldan, M. A. Aljuhani, M. S. Bootharaju, L. G. AbdulHalim, M. R. Parida, A.-H. Emwas, O. F. Mohammed and O. M. Bakr, *Angew. Chem., Int. Ed.*, 2016, **55**, 5749–5753.
- 241 J. Chai, S. Yang, Y. Lv, H. Chong, H. Yu and M. Zhu, *Angew. Chem., Int. Ed.*, 2019, **58**, 15671–15674.
- 242 X.-J. Xi, J.-S. Yang, J.-Y. Wang, X.-Y. Dong and S.-Q. Zang, *Nanoscale*, 2018, **10**, 21013–21018.
- 243 Z.-J. Guan, F. Hu, S.-F. Yuan, Z.-A. Nan, Y.-M. Lin and Q.-M. Wang, *Chem. Sci.*, 2019, **10**, 3360–3365.
- 244 J. Chai, Y. Lv, S. Yang, Y. Song, X. Zan, Q. Li, H. Yu, M. Wu and M. Zhu, *J. Phys. Chem. C*, 2017, **121**, 21665–21669.
- 245 M. Kim, Q. Tang, A. V. Narendra Kumar, K. Kwak, W. Choi, D.-e. Jiang and D. Lee, *J. Phys. Chem. Lett.*, 2018, **9**, 982–989.
- 246 Y. Negishi, K. Igarashi, K. Munakata, W. Ohgake and K. Nobusada, *Chem. Commun.*, 2012, **48**, 660–662.
- 247 N. Barrabés, B. Zhang and T. Bürgi, *J. Am. Chem. Soc.*, 2014, **136**, 14361–14364.
- 248 B. Zhang, S. Kaziz, H. Li, D. Wodka, S. Malola, O. Safonova, M. Nachtegaal, C. Mazet, I. Dolamic, J. Llorca, E. Kalenius, L. M. Lawson Daku, H. Häkkinen, T. Bürgi and N. Barrabés, *Nanoscale*, 2015, **7**, 17012–17019.
- 249 W. Du, X. Kang, S. Jin, D. Liu, S. Wang and M. Zhu, *Inorg. Chem.*, 2020, **59**, 1675–1681.
- 250 Z. Wang, R. Senanayake, C. M. Aikens, W.-M. Chen, C.-H. Tung and D. Sun, *Nanoscale*, 2016, **8**, 18905–18911.
- 251 X. Liu, G. Yao, X. Cheng, J. Xu, X. Cai, W. Hu, W. W. Xu, C. Zhang and Y. Zhu, *Chem. Sci.*, 2021, **12**, 3290–3294.
- 252 Y.-J. Kong, J.-H. Hu, X.-Y. Dong, Y. Si, Z.-Y. Wang, X.-M. Luo, H.-R. Li, Z. Chen, S.-Q. Zang and T. C. W. Mak, *J. Am. Chem. Soc.*, 2022, **144**, 19739–19747.
- 253 H. Yang, Y. Wang, J. Yan, X. Chen, X. Zhang, H. Häkkinen and N. Zheng, *J. Am. Chem. Soc.*, 2014, **136**, 7197–7200.
- 254 Y. Wang, H. Su, C. Xu, G. Li, L. Gell, S. Lin, Z. Tang, H. Häkkinen and N. Zheng, *J. Am. Chem. Soc.*, 2015, **137**, 4324–4327.
- 255 S. Jin, X. Zou, L. Xiong, W. Du, S. Wang, Y. Pei and M. Zhu, *Angew. Chem., Int. Ed.*, 2018, **57**, 16768–16772.
- 256 K. R. Krishnadas, A. Baksi, A. Ghosh, G. Natarajan and T. Pradeep, *ACS Nano*, 2017, **11**, 6015–6023.
- 257 L. Huang, J. Yan, L. Ren, B. K. Teo and N. Zheng, *Dalton Trans.*, 2017, **46**, 1757–1760.
- 258 H. Li, Y. Song, Y. Lv, Y. Yun, X. Lv, H. Yu and M. Zhu, *Inorg. Chem.*, 2019, **58**, 1724–1727.



- 259 X.-K. Wan, X.-L. Cheng, Q. Tang, Y.-Z. Han, G. Hu, D.-e. Jiang and Q.-M. Wang, *J. Am. Chem. Soc.*, 2017, **139**, 9451–9454.
- 260 Y. Wang, X.-K. Wan, L. Ren, H. Su, G. Li, S. Malola, S. Lin, Z. Tang, H. Häkkinen, B. K. Teo, Q.-M. Wang and N. Zheng, *J. Am. Chem. Soc.*, 2016, **138**, 3278–3281.
- 261 S. Wang, S. Jin, S. Yang, S. Chen, Y. Song, J. Zhang and M. Zhu, *Sci. Adv.*, 2015, **1**, e1500441.
- 262 J.-L. Zeng, Z.-J. Guan, Y. Du, Z.-A. Nan, Y.-M. Lin and Q.-M. Wang, *J. Am. Chem. Soc.*, 2016, **138**, 7848–7851.
- 263 Z.-J. Guan, J.-L. Zeng, S.-F. Yuan, F. Hu, Y.-M. Lin and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2018, **57**, 5703–5707.
- 264 Y. Song, Y. Li, H. Li, F. Ke, J. Xiang, C. Zhou, P. Li, M. Zhu and R. Jin, *Nat. Commun.*, 2020, **11**, 478.
- 265 T. Higaki, C. Liu, D. J. Morris, G. He, T.-Y. Luo, M. Y. Sfeir, P. Zhang, N. L. Rosi and R. Jin, *Angew. Chem., Int. Ed.*, 2019, **58**, 18798–18802.

