

Cite this: *Energy Adv.*, 2025,  
4, 152

# Reduced graphene oxide derived from the spent graphite anodes as a sulfur host in lithium–sulfur batteries†

J. Priscilla Grace,<sup>a</sup> Y. Kaliprasad<sup>b</sup> and Surendra K. Martha \*<sup>a</sup>

Lithium–sulfur batteries (LSBs) offer a distinctive advantage over traditional Li-ion batteries with a higher theoretical capacity (1675 mA h g<sup>-1</sup>) and energy density (2600 W h kg<sup>-1</sup>). This study focuses on an inexpensive graphite recycled from the spent LIBs as a promising sulfur host for developing sustainable LSBs. A recycled reduced graphene oxide–sulfur (RRGO-S) composite was cast onto a 3D-carbon fiber (CF) electrode (RRGO-S@CF). The flexible and lightweight RRGO-S@CF electrodes at 500 mA g<sup>-1</sup> delivered an initial discharge capacity of 552 mA h g<sup>-1</sup>, and there was no capacity loss in its initial five cycles, maintaining a stable capacity of 390 mA h g<sup>-1</sup> till 300 cycles with 73% capacity retention. At a higher current density of 1.675 A g<sup>-1</sup>, it delivered an improved capacity of 417 mA h g<sup>-1</sup>. The enhanced electrochemical performance was due to the favorable interaction between the RRGO and lithium polysulfides, reducing the active material loss and polysulfide dissolution. The 3D-CF and RRGO offer a conductive network and Li-ion transport with electrolyte wettability, thereby improving the sulfur utilization and overall electrochemical performance in LSBs. This approach demonstrates the construction of recycled materials from the spent LIBs as an inexpensive source to meet the growing energy demand in the practical development of LSBs.

Received 29th July 2024,  
Accepted 6th November 2024

DOI: 10.1039/d4ya00480a

rsc.li/energy-advances

## 1. Introduction

The revolutionized lithium-ion battery technology has been commercialized in the energy market till today, although these batteries can hardly store up to 250 W h kg<sup>-1</sup>.<sup>1</sup> Thus, it is difficult to meet today's energy demand due to their limited capacity of the cathodes (140–200 mA h g<sup>-1</sup>) and energy density. The innovative power sources are poised to redefine the future of energy storage systems.<sup>2–4</sup> Lithium–sulfur batteries (LSBs) offer a distinctive advantage over traditional Li-ion batteries with their higher theoretical capacity (1675 mA h g<sup>-1</sup>) and energy density (2600 W h kg<sup>-1</sup>).<sup>5,6</sup> Sulfur is the 5th most common element on earth. It is eco-friendly and inexpensive, making it an alternative energy storage electrochemical system that can reach a high energy density beyond 500 W h kg<sup>-1</sup>. Unfortunately, LSB is inherently challenging, hindering its commercialization.<sup>7</sup> The main issue arises due to the insulating nature of sulfur, and the discharged products (Li<sub>2</sub>S) limit

the utilization of sulfur. Another problem is the dissolution of polysulfides in the electrolyte that shuttle between the cathode and anode, leading to the loss of active material. Further, the volume expansion of sulfur (~80%) causes the detachment of polysulfides from the cathode, leading to fast capacity decay during cycling and low efficiency.<sup>8–10</sup> To overcome the shortcomings of LSBs, various carbon materials have been employed as ESI,† (host material) for sulfur cathodes to improve the electrical conductivity of sulfur by trapping the soluble polysulfides upon cycling.<sup>11,12</sup>

Designing a carbon host, such as porous carbon, graphene, carbon nanotubes, and carbon nanofibers, as a conductive framework improves the electrochemical performance of LSBs. Fabrication of carbon/sulfur composite is a promising sulfur cathode design that embeds sulfur into the carbon frameworks, thus exhibiting excellent electrical conductivity and good mechanical stability.<sup>13–15</sup> The various carbon structures exhibit excellent properties, including confining polysulfides within its matrices by avoiding the diffusion of Li<sub>2</sub>S<sub>n</sub> in the electrolyte, reducing the loss of active materials and improving the cycle life and conductivity by providing a conductive network, and accommodating volume expansion of active materials upon cycling, which substantially benefits the electrochemical performance of LSBs.<sup>16–18</sup>

Many studies have recently focused on these materials due to the unique benefits of graphene oxide in the LSB cathode.

<sup>a</sup> Department of Chemistry, Indian Institute of Technology Hyderabad, Kandi, Sangareddy, Telangana 502284, India. E-mail: martha@chy.iith.ac.in

<sup>b</sup> Nile Limited, Lot No. 24 A/A, MLA Colony, Road No. 12, Banjara Hills, Hyderabad, India

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ya00480a>



Due to their porous network, aligned nanosheets with good electrical conductivity, high surface area, and chemical stability with oxygen-containing functional groups, the graphene oxide in the LSB cathode helps transport electrons and ions by shortening the diffusion pathways and immobilizing by suppressing the dissolution of polysulfides.<sup>19–22</sup> Previous studies have reported that the graphene-wrapped sulfur (GWS) shows a reversible capacity of 808 mA h g<sup>-1</sup> at 210 mA g<sup>-1</sup> with 98% Coulombic efficiency over 100 cycles.<sup>19</sup> Similarly, the reduced graphene oxide (RGO)-sulfur composite delivers an initial discharge capacity of 1385 mA h g<sup>-1</sup> at 0.1C rate with 45% capacity retention for up to 100 cycles.<sup>23</sup> A graphene-wrapped hair-derived carbon-sulfur composite delivers an initial discharge capacity of 1113 mA h g<sup>-1</sup> at 0.2C with 89% capacity retention for up to 300 cycles.<sup>24</sup> ESI,† Table S1 shows a literature survey of RGO-S composite electrode electrochemical performances in terms of capacities, capacity retention, and cycle number in comparison to the present work.

The demand for graphite is continually increasing by 10–12% each year. Therefore, various carbon sources have been derived mechanistically using differing treatment strategies. Several recycling techniques have been adopted for green waste and spent LIBs electrode materials by post-treatment procedures.<sup>25</sup> Currently, there is a progressive usage of LIBs due to the increasing energy demand. This leads to the massive disposal of LIB waste, thus resulting in environmental pollution with serious hazards.<sup>26,27</sup> Therefore, reusing or recycling the spent LIB electrode materials is a potential approach to pave the way for better sustainable energy storage systems. A publication from our group observed that recycled graphene has a surface area of 9.12 m<sup>2</sup> g<sup>-1</sup> with a pore volume of 1.94 × 10<sup>-2</sup> cc g<sup>-1</sup>. A recycled water-washed graphite and graphene nanoflake composite had an average discharge capacity of 320 mA h g<sup>-1</sup> over 1000 cycles with 62% capacity retention at a higher current density of 500 mA g<sup>-1</sup>.<sup>28</sup> Recycling graphite from the inexpensive spent LIBs with cost-effective purification methods has been employed, which is expected to be successful in LIBs and the forthcoming LSBs.<sup>29</sup>

The active material sulfur content dramatically influences the enhancement of the electrochemical performance in the cathode. The low sulfur content reduces the overall energy density of LSB. The increase in the sulfur content reduces the conductivity of the electrode.<sup>30</sup> To balance specific capacity and the cathode's stability,<sup>31,32</sup> recycled reduced graphene oxide (RRGO) derived from LIB spent graphite anode with 3D-carbon fiber (CF) porous network architecture is employed in this work, beyond the traditional sulfur cathode, to develop RRGO-sulfur composite cathode. This electrode architecture assists in achieving stable electrochemical performance with optimal sulfur content and good capacity.<sup>33</sup> The 3D-CF free-standing electrode is flexible and lightweight, and replaces the traditional metallic aluminum current collector.<sup>34</sup>

In this work, we report the application of a simple, effective, promising sulfur composite material on a 3D-CF as a cathode for LSB. The recycled reduced graphene oxide has been synthesized from the graphite of recycled LIBs by Hummers' method,

and the sulfur composite is obtained by melt-diffusion. The self-supported flexible RRGO-S@3D-CF electrode architecture provides fast electron and lithium ion transport, enables effective active material utilization with effective electrolyte infiltration, and accommodates volume expansion with good mechanical stability.<sup>35–37</sup> This approach demonstrates the construction of recycled materials from the spent LIBs as an inexpensive source to meet the growing energy demand in the practical development of LSBs.

## 2. Experimental methods

### 2.1. Synthesis of recycled reduced graphene oxide (RRGO) and RRGO-sulfur composite (RRGO-S)

The commercially spent LIBs (18 650 cells) from the laptop battery pack (supplied by our industry partner Nile Limited, Hyderabad, India) were disassembled and discharged to less than 2.0 V. The cells were dismantled manually, and the graphite from the copper foil current collector was washed with water (as water binders are used for the graphite anode), dried in a hot air oven at 100 °C for 12 h, and further heated at 750 °C in a nitrogen atmosphere to remove the organic impurities (denoted as retrieved graphite).<sup>26,28</sup> The retrieved graphite is converted to graphene oxide by the Hummers' method<sup>38</sup> and thermal reduction of the retrieved graphite to reduced graphene oxide under an inert atmosphere at 500 °C for 30 min (denoted as recycled reduced graphene oxide (RRGO)).

60% sulfur (Sigma-Aldrich) and 30% RRGO are mixed thoroughly and heated in an argon-filled Schlenk tube at 160 °C for 6 h for melt-diffusion to obtain the RRGO-S composite (ESI,† Fig. S1 and Scheme 1).


### 2.2. Physical characterization

The physical characterization was carried out for the RRGO-S composite and RRGO-S@CF electrode. The XRD (X-ray diffraction) patterns were obtained and analyzed using a Malvern Panalytical X'Pert<sup>3</sup> (Netherlands) diffractometer in the 2 theta range of 10°–80°. Raman spectra were measured in a Witec Raman confocal spectrometer using a laser excitation source of 532 nm. The XPS analysis was carried out in ESCA+ (Kratos AXIS Nova, Shimadzu Japan) with the monochromic Al K $\alpha$  (1486.6 eV), and it was fitted using Origin software (9.0). Morphology of the synthesized material is analyzed using a JEOL-211 (200 kV) scanning electron microscope (SEM). Thermogravimetric analysis (TGA) was conducted with a SDT Q600, Germany instrument under a nitrogen atmosphere at a heating rate of 10 °C min<sup>-1</sup> to measure the weight loss of sulfur.

### 2.3. Fabrication of electrodes

The slurry was prepared with 90% RRGO-S composite, 10% PVDF binder, and 1,2-*N*-methyl pyrrolidone (NMP) as the solvent. The slurry was coated onto CF sheets, dried, punched into 12 mm electrodes, dried further in a vacuum oven at 70 °C



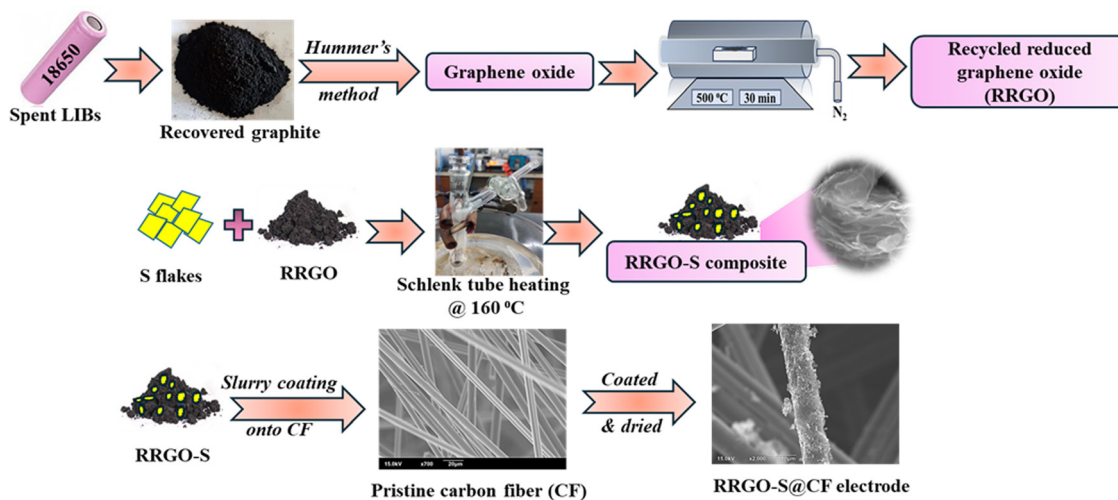

Scheme 1 Schematic of the overall synthesis of the RRGO-S composite and the preparation of the RRGO-S@CF electrodes.

for 12 h, and calendered. The active material loading (sulfur) is  $2 \text{ mg cm}^{-2}$ . Moreover, high-loading sulfur ( $\sim 4.5 \text{ mg cm}^{-2}$ ) cells were also tested for comparison.

#### 2.4. Electrochemical characterization

As working electrodes, the RRGO-S@CF electrodes were pressed and fabricated in the CR2023 coin cell inside the glove box ( $\text{O}_2$  and  $\text{H}_2\text{O}$  levels  $\leq 2$  ppm, mBraun). Lithium metal (10 mm diameter chip) was used as a reference and counter electrode, GF/D as a separator, and, 1 M LITFSI and DOL: DME (1 : 1, V/V) with 0.1 M  $\text{LiNO}_3$  were used as the electrolyte. The galvanostatic charge–discharge cycling was carried out in a Biologic BCS-805 battery tester in the range between 1.5–2.8 V. Cyclic voltammetry (CV) and electrochemical impedance spectra (EIS) studies were conducted in the Solartron multi-channel cell test system (1470E multichannel potentiostat coupled with 1455A frequency response analyzers) at a scan rate of  $0.05 \text{ mV s}^{-1}$  (1.5–2.8 V) and a frequency range of 1 MHz to 0.01 Hz at a voltage perturbation of 5 mV.

### 3. Results and discussion

The XRD plot (Fig. 1a) of recycled reduced graphene shows a graphitic peak with a broad hump for the (002) plane at  $24.1^\circ$ . The broad hump manifests the considerable interlayer distance and the randomness of the RRGO. The RRGO-S composite synthesized by the melting-diffusion process exhibits an intense peak from  $20^\circ$  to  $30^\circ$  for the diffraction of sulfur (JCPDS no. 08-0247), confirming the orthorhombic crystal structure, which overshadowed the RRGO graphitic peaks around  $24.1^\circ$ . This shows that the sulfur is mainly on the surface of the amorphous layer of RRGO. The Raman spectra (Fig. 1b) of the RRGO-S composite show the D and G bands of RRGO at  $1348$  and  $1586 \text{ cm}^{-1}$ , respectively, which are due to the vibration of  $\text{sp}^2$  bonded carbon atoms. However, no sulfur peaks are detected due to the masking of RRGO. The  $I_D/I_G$  ratio of RRGO is  $\sim 2$  ( $> 1$ ), depicting the disorder of the RRGO (ESI,† Fig. S3). Fig. 1c shows the Raman spectra of pure sulfur ( $\text{S}_8$ ) with the S–S bonds at  $154$ ,  $188$ ,  $248$ ,  $439$ , and  $474 \text{ cm}^{-1}$ , which matches the literature. The XRD and Raman spectra define the sulfur

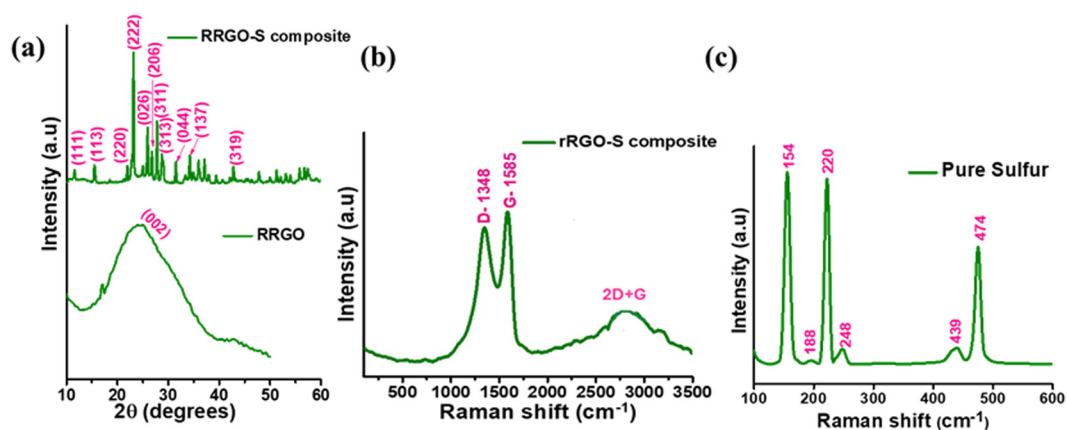


Fig. 1 (a) XRD plots of the RRGO and RRGO-S composite. (b) and (c) Raman spectra of the RRGO-S composite and pure sulfur.



insertion into the RGO layers.<sup>39</sup> The XRD pattern (ESI,† Fig. S2a) of water-washed graphite clearly shows a sharp (002) peak at 26.5° for a hexagonal crystal lattice of the graphite. The Raman spectrum (ESI,† Fig. S2b) demonstrates a flat D band at 1360 cm<sup>-1</sup> and a G band at 1575 cm<sup>-1</sup>, and an I<sub>D</sub>/I<sub>G</sub> ratio of 0.54, thus depicting a disordered graphitic phase of the water-washed graphite.

The XPS analysis was carried out to understand the surface chemical compositions and elements in the RRGO-S@CF electrodes. The survey scan of RRGO-S@CF (Fig. 2a) shows the presence of the S 2p, S 2s, C 1s, and O 1s spectra. The C 1s spectra (Fig. 2b) show peaks at 284.6, 285.6, 289 and 290 eV for C–C, C–O, C=O and  $\pi$ - $\pi^*$  transition bonds in the compounds, respectively.<sup>40</sup> The O 1s spectra (Fig. 2c) exhibit peaks at 531.9 eV and 533.6 eV for the S=O and C=O bonds, respectively. The successful infusion of sulfur is manifested by the S 2p spectra, revealing peaks at 163.9, 165, 167, 168.2, and 169 eV for the S 2p<sub>3/2</sub>, S 2p<sub>1/2</sub>, S–O, and C–S bonds, respectively. The S–O bonds show sulfur oxidation with the functional groups of reduced graphene oxide. The C–S bond in O 1s and S 2p reveals the chemical bonding between the RGO and sulfur after the infusion of sulfur. The functional groups on the RRGO highly enhance the binding of sulfur in the C–C bond. The high-resolution F 1s spectra are provided in ESI,† Fig. S4. These chemical bonds show the dispersed sulfur in RRGO onto the 3D-CF electrode, thus immobilizing the dissolution of polysulfides into the electrolyte, preventing the loss of sulfur, and improving the cycling stability of the sulfur cathode (as discussed later in the electrochemistry section).

The BET surface area of CF and RRGO-S@CF is 1 m<sup>2</sup> g<sup>-1</sup> and 11 m<sup>2</sup> g<sup>-1</sup>. The pore volume of CF and RRGO-S@CF is 0.008035 cm<sup>3</sup> g<sup>-1</sup> and 0.053174 cm<sup>3</sup> g<sup>-1</sup>. The pore volume and adsorption–desorption curves are provided in ESI,† Fig. S5.

The SEM image of the RRGO-S composite (Fig. 3a–c) shows the graphitic layered microstructures of RRGO. Similar to the broad hump in the XRD pattern (Fig. 1a) for RRGO-S, the SEM images manifested the amorphously arranged graphene sheets along with the dispersed sulfur in the RRGO, which signifies the composite comprising both sulfur and carbon (EDAX images in ESI,† Fig. S6). The exfoliated graphene sheets not only provide a large surface area (93 m<sup>2</sup> g<sup>-1</sup>) with more gaps, but also furnish an adsorption site for anchoring polysulfides with effective electrolyte impregnation and Li-ion transport.<sup>41</sup> The RRGO-S slurry is coated onto the 3D-CF electrode. Fig. 3d and e shows that the composite of RRGO-S looks like a graphene sheet with sulfur adsorbed to the wall of the CF matrix, which gives a good adhesion between the active material and conductive network. As shown in Fig. 3g–i, the EDAX of RRGO-S@CF depicts the uniform dispersion of carbon and sulfur onto the CF. Therefore, the morphology result suggests that the sulfur is well dispersed in the composite and on the CF network. Fig. S6c (ESI†) shows the SEM of the water-washed graphite, displaying a smooth surface having graphite particle sizes of ~10–20  $\mu$ m (ESI,† Fig. S2d). The TGA curves of the RRGO-S (ESI,† Fig. S7) composite indicate the loss of sulfur from 160 °C to 250 °C, confirming a 60% loss of sulfur, thus manifesting a loading of sulfur (60%) in the RRGO-S composite.

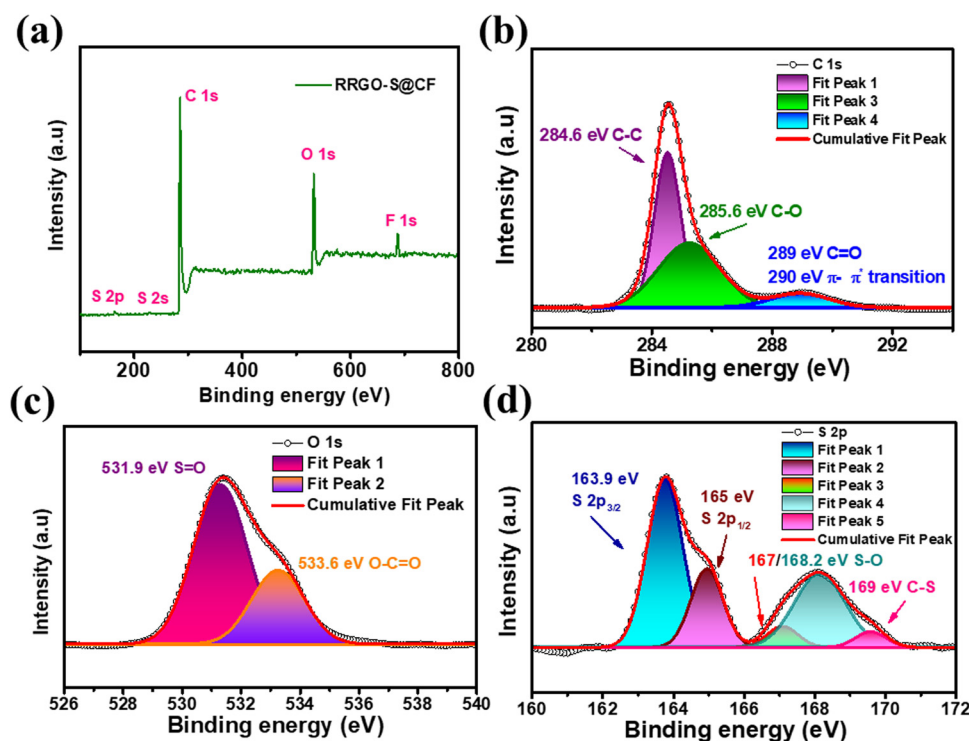


Fig. 2 XPS of the RRGO-S@CF electrode: (a) survey scan, (b) C 1s, (c) O 1s, (d) S 2p. The binding energy was calibrated with respect to the C 1s peak of 284.6 eV.



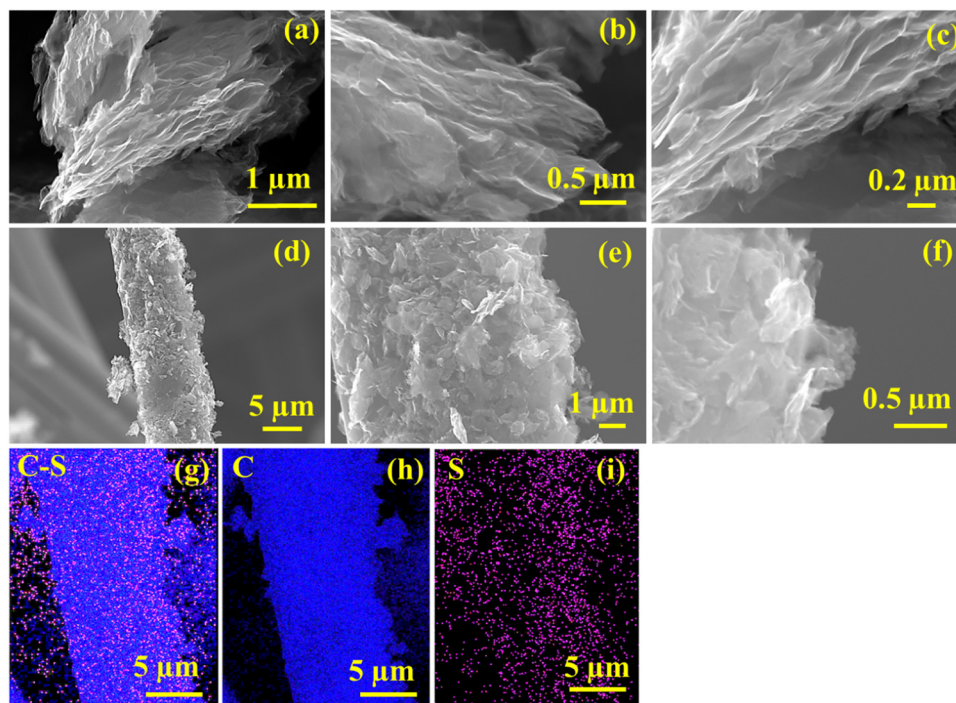


Fig. 3 SEM image of (a)–(c) RRGO-S, (d)–(f) RRGO-S@CF, and its corresponding EDAX images: (g) C–S, (h) C and (i) S.

The CV plot of RRGO-S@CF (Fig. 4a) in the initial scan shows two peaks at the cathodic region around 2.34 and 2.01 V for the reduction of higher-order polysulfides ( $\text{Li}_2\text{S}_8$ ) to soluble  $\text{Li}_2\text{S}_6/\text{Li}_2\text{S}_4$  and the insoluble  $\text{Li}_2\text{S}/\text{Li}_2\text{S}_2$ , and the split peak in the anodic region at 2.48 and 2.51 V is for the subsequent conversion of lithium sulfide to lithium polysulfides and to sulfur ( $\text{S}_8$ ). These split peaks in the anodic scan are caused by increased electrolyte viscosity due to the dissolution of polysulfides in the initial cycles. There is a slight shift in the 5th cycle due to the rearrangement of sulfur to its more stable site. The small peak shift, the high peak current under the curve, and the oxidation/reduction peaks manifest improved reversibility with improved Li-ion kinetics and the electrochemical stability of the electrode. Like the CV curves, the galvanostatic charge–discharge cycling shows two voltage plateaus in the discharge curve for the transformation of  $\text{S}_8$  to higher-order intermediate soluble polysulfides to insoluble lithium sulfides.<sup>42</sup> The RRGO-S@CF delivers  $873 \text{ mA h g}^{-1}$  (Fig. 4b and c) in its 1st cycle with no negligible capacity loss in its initial five cycles, showing  $774 \text{ mA h g}^{-1}$  in its 20th cycle and maintaining  $447 \text{ mA h g}^{-1}$  for up to 100 cycles at  $200 \text{ mA g}^{-1}$  with 99% Coulombic efficiency. From the ESI,<sup>†</sup> in Fig. S8(a) and (b), the calculated energy densities of the 1st and the 100th cycle are  $1834$  and  $1455 \text{ W h kg}^{-1}$ , respectively. Similarly, in ESI,<sup>†</sup> Fig. S8(c), the voltage hysteresis plots of the 1st and 200th cycle show that the voltage difference between the charge–discharge cycles are 0.22 and 0.18 V, respectively. The decrease in voltage in the 100th cycle (after cycling) depicts lower polarization, which suggests a smaller barrier during the efficient kinetics of the RRGO-S@CF electrodes, thus displaying a

decreased resistance and an intimate contact between the RRGO and sulfur by chemical adsorption, and effectively suppressing the dissolution of polysulfides in the electrolyte during the charge–discharge cycling.<sup>43</sup>

At a current density of  $500 \text{ mA g}^{-1}$  (Fig. 4d and e), the initial discharge capacity is  $552 \text{ mA h g}^{-1}$ . There is no capacity loss in their initial five cycles, showing  $502 \text{ mA h g}^{-1}$  in its 20th cycle. Furthermore, it maintains a stable capacity of  $447 \text{ mA h g}^{-1}$  for up to 150 cycles with 81% capacity retention and 73% capacity retention at the end of the 300th cycle with a Coulombic efficiency of  $>99\%$ . The cyclic stability plot (Fig. 4c and e) of RRGO-S@CF (capacity vs. cycle number) also displays stable cycling for up to 100 and 300 cycles. In contrast, the RRGO-S on carbon-coated aluminum (RRGO-S@C-Al electrode) (ESI,<sup>†</sup> Fig. S9) at  $500 \text{ mA g}^{-1}$  delivers an initial discharge capacity of  $670 \text{ mA h g}^{-1}$  with 5% capacity loss in their 2nd cycle. It provides a capacity of  $300 \text{ mA h g}^{-1}$  (45% capacity retention) at the end of 100 cycles, which is much less compared to the stable RRGO-S@CF electrodes. Similarly, at a high current density of  $800 \text{ mA g}^{-1}$  (Fig. 4f), the RRGO-S@CF electrodes provide an initial discharge capacity of  $535 \text{ mA h g}^{-1}$  and deliver a capacity of  $390 \text{ mA h g}^{-1}$  even after 400 cycles with a capacity retention of 73% and 60% at the 500th cycle. Even a higher sulfur loading of  $\sim 4.5 \text{ mg cm}^{-2}$  (Fig. 4g) at  $500 \text{ mA g}^{-1}$  shows an initial discharge capacity of  $575 \text{ mA h g}^{-1}$ , delivering a stable capacity of  $457 \text{ mA h g}^{-1}$  after 130 cycles with 99% Coulombic efficiency. Cyclic stability plots of the specific and volumetric discharge capacities at  $800 \text{ mA g}^{-1}$  are given in ESI,<sup>†</sup> Fig. S10. The volumetric capacities are  $\sim 30\%$  lower than the gravimetric capacities.



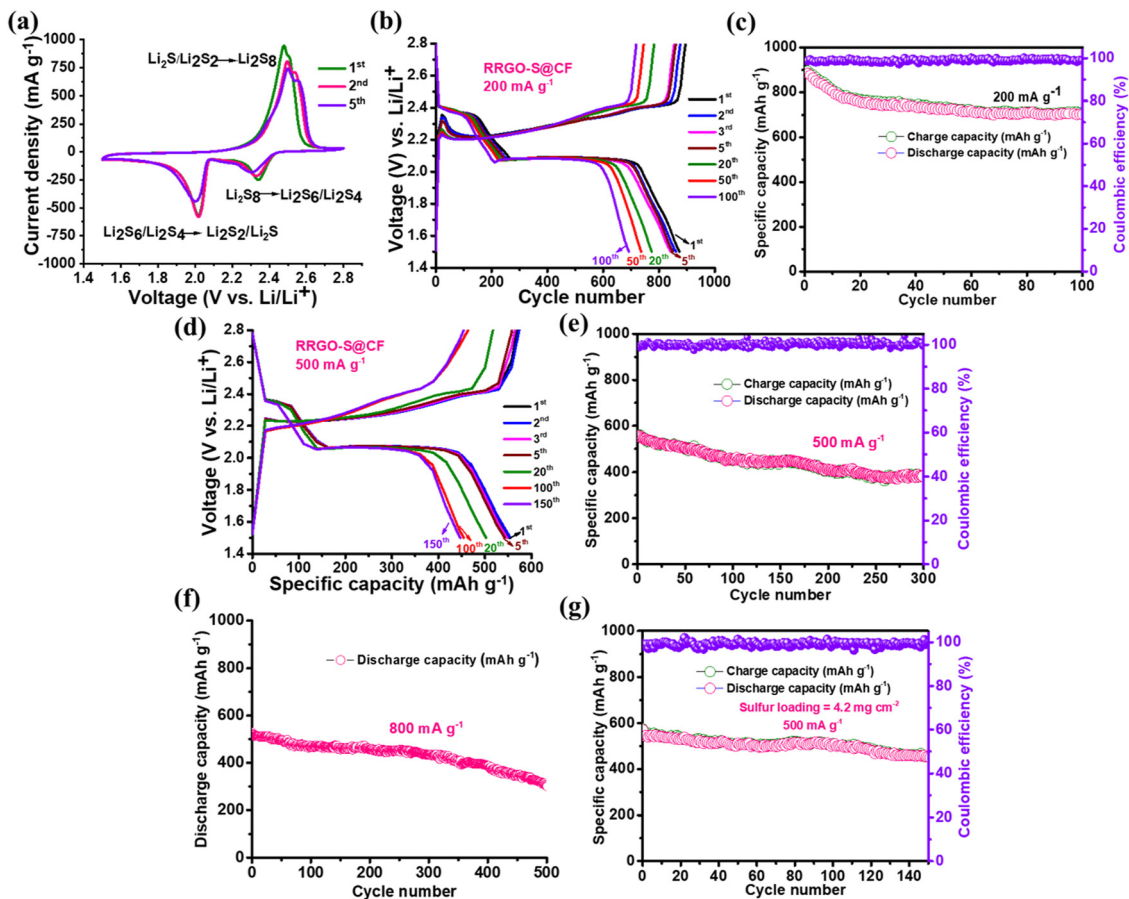


Fig. 4 (a) CV plot of RRGO-S@CF. (b) GCD curves of RRGO-S@CF at  $200 \text{ mA g}^{-1}$ . (c) Cycle stability of RRGO-S@CF at  $200 \text{ mA g}^{-1}$  with Coulombic efficiency. (d) GCD curves of RRGO-S@CF at  $500 \text{ mA g}^{-1}$ . (e) Cyclic stability plot at  $500 \text{ mA g}^{-1}$  with Coulombic efficiency ( $\sim 4.5 \text{ mg cm}^{-2}$ ). (f) Cyclic stability plot of RRGO-S@CF at  $800 \text{ mA g}^{-1}$  ( $2 \text{ mg cm}^{-2}$ ) and (g) GCD curve of sulfur at higher loading of  $\sim 4.5 \text{ mg cm}^{-2}$  at  $500 \text{ mA g}^{-1}$  with Coulombic efficiency.

The rate capability plot of RRGO-S@CF (Fig. 5a and b) at different specific currents of 50, 100, 200, 300, 500, 800, 1000, 1500 and  $1675 \text{ mA g}^{-1}$  delivers excellent capacities of 1113, 985, 875, 730, 572, 540, 489, 435 and  $417 \text{ mA h g}^{-1}$ , respectively. Even at a high specific current of 1.5 and  $1.6 \text{ A g}^{-1}$ , the composite delivers an improved capacity of 435 and  $417 \text{ mA h g}^{-1}$ . Upon increasing the current density, the stability of the battery also increases.<sup>44</sup> As the specific current increases, the sulfur active material may be further activated. Thereby, the polarization effect decreases and may promote more polysulfide conversion by delivering stable capacity. The C-rate performance for the  $4.5 \text{ mg cm}^{-2}$  active material loading (ESI<sup>†</sup>; Fig. S11b) is demonstrated at 100, 200, 300, 500, 800, 1000 and  $1500 \text{ mA g}^{-1}$  specific currents, and exhibits 990, 886, 742, 580, 547, 498 and  $443 \text{ mA h g}^{-1}$  capacities, respectively. To understand the advantage of the RRGO-S@CF cells, a self-discharge study was performed after a fully charged condition, followed by 100 h in open circuit condition at  $25 \text{ }^\circ\text{C}$  (ESI<sup>†</sup>; Fig. S12). The RRGO-S@CF cathode exhibits a stable OCV of  $\sim 2.32 \text{ V}$  during storage due to a reduction in the polysulfide shuttle effect. Before and after self-discharge, the cell maintains a capacity of 878 density and  $691 \text{ mA h g}^{-1}$  (20% loss of capacity), respectively (ESI<sup>†</sup>; Fig. S12b).

The RRGO-S@CF electrode reveals better electrochemical performance in LSBs at different current densities. The enhanced cycle performance and rate capability performance are due to the graphene network and 3D-CF, which contributes to the electronic conductivity that accelerates the ion transfer process (fast reaction kinetics), thus providing an intimate contact between the oxygen functional groups of RRGO and sulfur. Furthermore, it serves as polysulfide immobilizers by limiting the concentration of polysulfides in the electrolyte, and reduces the shuttle effect. The 3D-CF has an internal void space that offers good electrolyte infiltration, good Li-ion kinetics, and high sulfur utilization, alleviating the volume expansion. A plausible mechanism is given in the schematic shown in Scheme 2. The RGO-S composite from various literature studies, along with the capacities, capacity retention, cycle number, *etc.*, are compared with our work (provided in ST1, ESI<sup>†</sup>).

The EIS analysis of RRGO-S@CF (Fig. 5c) for the 1st and the 150th cycle demonstrates two semicircles, which are for the high and middle-frequency regions as charge transfer resistances of sulfur intermediates, followed by the other semicircle for  $\text{S}_8$  and  $\text{Li}_2\text{S}$  dissolution in the electrolyte, and the low-frequency straight line for lithium-ion diffusion ( $W_0$ ). The  $R_s$




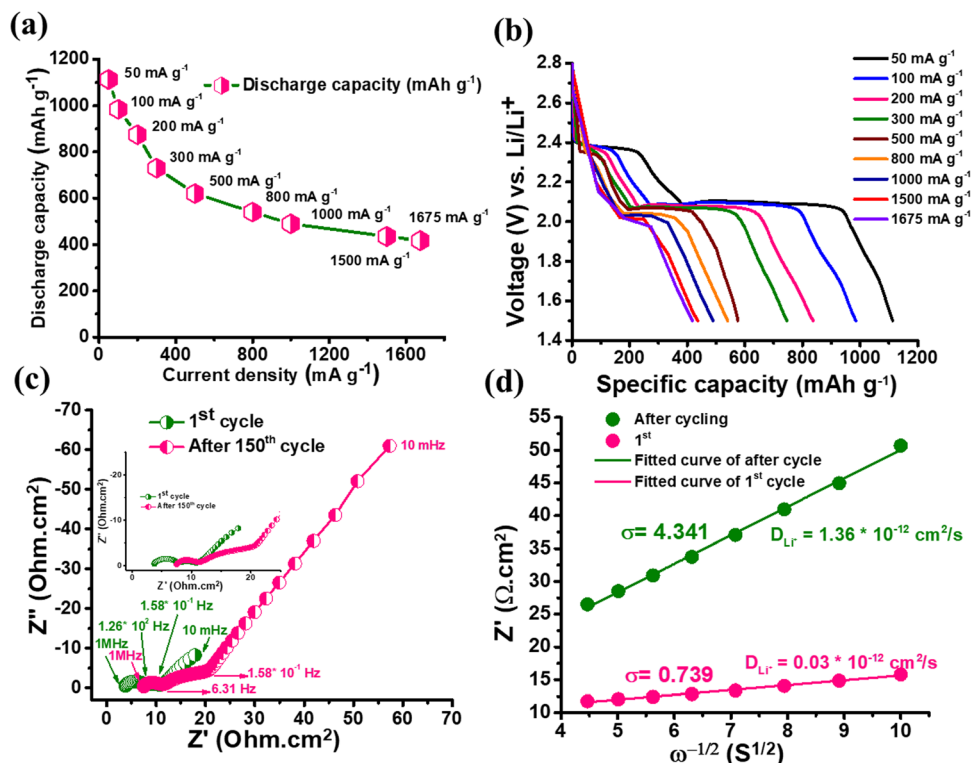


Fig. 5 (a) and (b) Rate capability plot at different current densities. (c) EIS spectra of RRGO-S@CF for the 1st and 150th cycle (cycling at  $200 \text{ mA g}^{-1}$ ) with their frequencies. (d) Plot of  $Z''$  vs.  $\omega^{-1/2}$  ( $\text{S}^{1/2}$ ) in the low-frequency region.

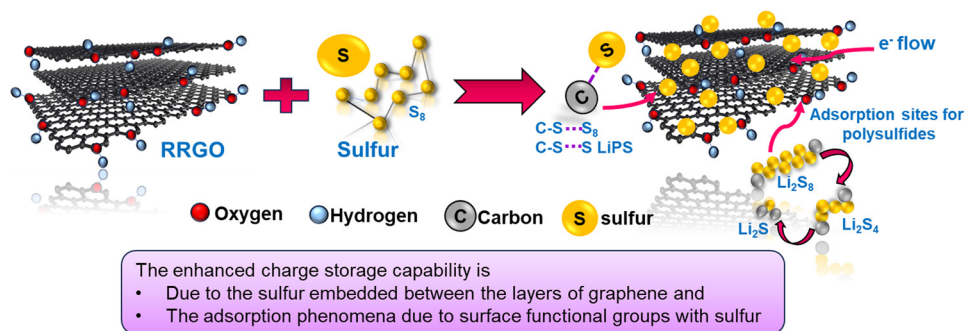

Scheme 2 Schematic of the mechanism of RRGO with sulfur.

and high frequency semi-circle values of the 1st cycle are 3.75 and  $4 \Omega \text{ cm}^2$ , respectively. For the 150th cycle, the values are 7.5 and  $4 \Omega \text{ cm}^2$ , respectively. The slight increase in the  $R_s$  value is due to the ohmic losses as a result of the dissolution of sulfur in the electrolyte. There is almost no change in the charge transfer resistance of the RRGO-S@CF electrode. This may be due to the better electronic conductivity of RRGO, which accelerates the electron transfer reactions during cycling. The 3D-CF effectively accommodates the volume expansion due to the  $\text{Li}_2\text{S}$  formation and enhanced Li-ion kinetics by efficient electrolyte infiltration into its network, maintaining the integrity of the electrode.<sup>45</sup> The  $D_{\text{Li}^+}$  (lithium diffusion coefficient) can be calculated from the relationship between the Warburg

impedance ( $W$ ) and the inverse square root of the angular frequency ( $\sigma$ ). The equation,  $D_{\text{Li}^+} = \frac{R^2 T^2}{2A^2 N^2 F^4 C^2 \sigma^2}$ <sup>46,47</sup> is used to calculate the value of  $D_{\text{Li}^+}$ , where  $R$  is the gas constant,  $T$  is the absolute temperature in kelvin,  $A$  is the geometrical area of the electrode in  $\text{cm}^2$ ,  $N$  is the number of electron transport during redox reaction,  $F$  is the Faraday's constant (96 500 Coulombs),  $C$  is the molar concentration of lithium ions ( $0.049 \text{ mol cm}^{-3}$ ), and  $\sigma$  is the Warburg impedance factor. The plot of  $\omega^{-1/2}$  vs. the slope of  $Z'$  gives the value of  $\sigma$ . The diffusion coefficient (Fig. 5d) value of  $3 \times 10^{-10} \text{ cm}^2 \text{ s}^{-1}$  in the first cycle indicates the excellent conductivity of the RRGO-S electrode, significantly enhancing the Li-ion diffusion. The Li-ion



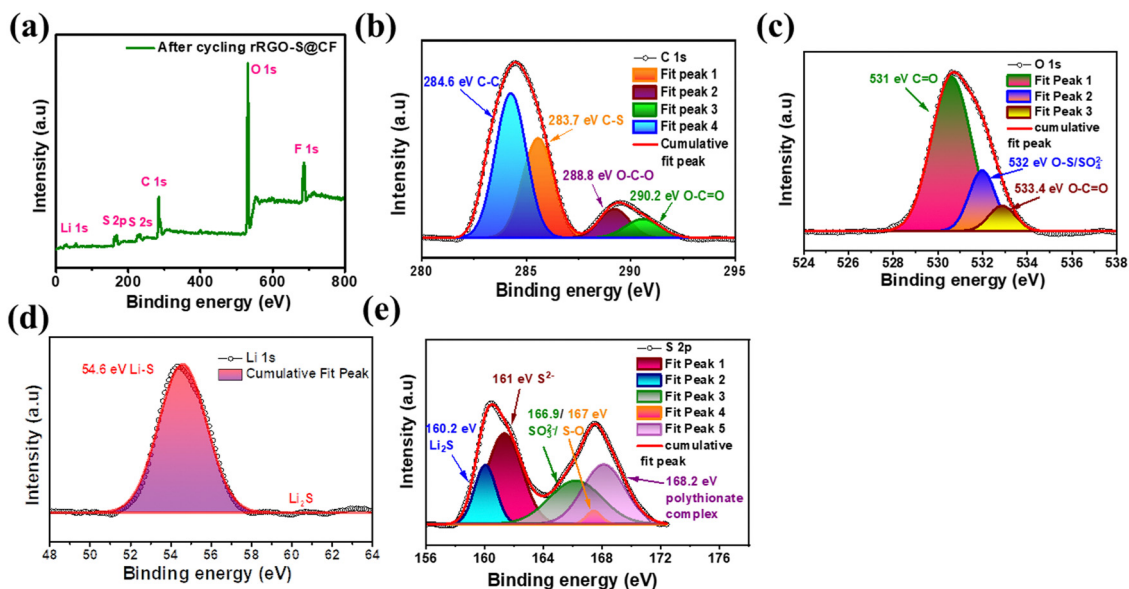


Fig. 6 XPS of the post-cycled (after 150 cycles) RRG0-S@CF: (a) survey scan, (b) C 1s, (c) O 1s, (d) Li 1s, and (e) S 2p.

diffusion for similar electrodes was reported in the literature to be much lower than in the current work,<sup>48</sup> and the improved diffusion coefficient tends to enhance the electrochemical performance in terms of the cycle stability and C rate.

The XPS of the post-cycled RRG0-S@CF electrode is shown in Fig. 6a. The survey scan shows the presence of Li 1s, S 2p, S 2s, C 1s, O 1s, and F 1s spectra. As indicated in Fig. 6b, the C 1s spectra show the peaks at 284.6, 283.7, 288.8, and 290.2 eV for the C-C, C-S, O-C-O, and O-C=O bonds, respectively. Fig. 6c shows the O 1s spectra, which exhibit 531, 532, and 533.4 eV peaks for the C=O, O-S/SO<sub>4</sub><sup>2-</sup>, and O-C=O bonds, respectively. Fig. 6d shows the Li 1s spectra, where the Li-S bond at 54.6 eV is due to the chemical interaction of lithium and polysulfides and its Li<sub>2</sub>S deposition. Fig. 6e shows the S 2p spectra, which display peaks at 160.2, 161, 166.9, 167, and

168.2 eV for the Li<sub>2</sub>S, S<sup>2-</sup>, SO<sub>3</sub><sup>2-</sup>/S-O, and polythionate complex bonds, respectively. These features are attributed to the infiltration of the electrolyte during cycling.<sup>49</sup> The S-O bonds confirm the interaction between the oxygen groups and soluble lithium polysulfides.

The postmortem SEM images of the cycle RRG0-S@CF (Fig. 7a-c) depict the formation of lithium sulfide particles in the 3D-CF network, which is different from the before-cycling SEM of RRG0-S@CF (shown in Fig. 3a). Therefore, it manifests the integrity of the 3D-CF electrode. Furthermore, the RRG0 provides a better network that prevents the polysulfides from collapsing even after cycling, which effectively accommodates the polysulfide and better Li-ion kinetics by providing sufficient electrolyte into its 3D-CF network. The formation of Li<sub>2</sub>S on the CF electrodes is depicted in the EIS after cycling (Fig. 5c),

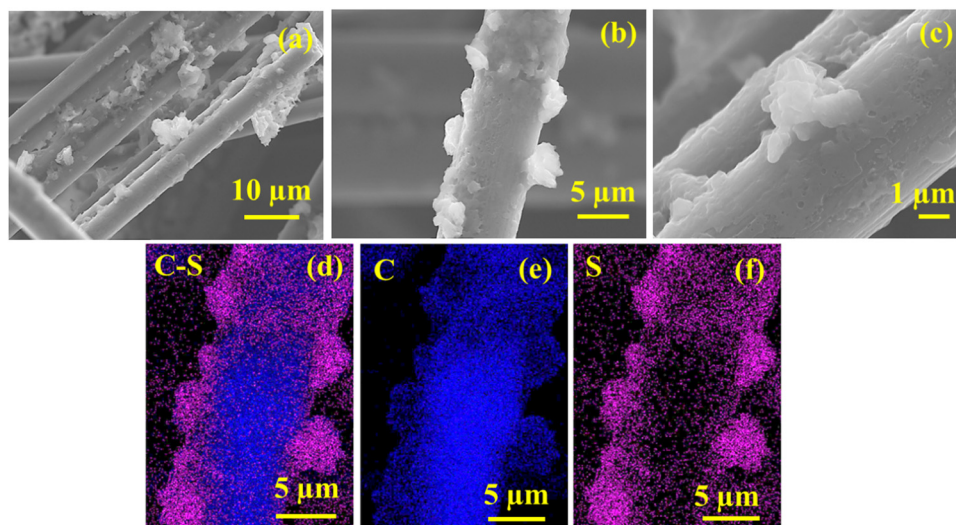


Fig. 7 Post-cycled SEM images of the (a)–(c) cycled RRG0-S@CF electrodes and their EDAX images of (d) C-S, (e) C, and (f) S.



resulting in a slight increase in  $R_{CT}$ . The EDAX (Fig. 7d–f) shows the uniform distribution of C–S, C, and S on the 3D-CF network even after cycling. Therefore, RRGO-S@CF maintains its structural integrity during the charge–discharge cycling.

Overall, the recycled reduced graphene oxide (RRGO) provides good conductivity that engages the electron transfer reaction and gives good accessibility for both electron and ion transfer. The oxygen functional groups contribute toward the excellent interaction with sulfur, thereby limiting the dissolution of polysulfides. The 3D-CF and RRGO offer a porous conductive network and Li-ion transport with electrolyte wettability, thereby improving the sulfur utilization and overall electrochemical performance in LSBs. This is further demonstrated in the EIS, postmortem SEM, and XPS analyses. This study describes an inexpensive graphite material recycled from the spent LIBs, which shows promise as a cathode host material for developing sustainable LSBs.

## 5. Conclusions

This study describes an inexpensive graphite material recycled from the spent LIBs, which will be a promising cathode host material for developing sustainable LSBs. The RRGO-S composite is synthesized by a melt-diffusion process and cast onto the 3D-CF electrode (RRGO-S@CF). At a current density of  $500 \text{ mA g}^{-1}$ , the initial discharge capacity is  $552 \text{ mA h g}^{-1}$ . There is no capacity loss in their initial five cycles. The material displays  $502 \text{ mA h g}^{-1}$  in its 20th cycle and maintains a stable capacity of  $447 \text{ mA h g}^{-1}$  for up to 150 cycles with 81% capacity retention and 73% capacity retention at the end of the 300th cycle. Even at a high current density of  $1.675 \text{ A g}^{-1}$ , RRGO-S@CF delivers an improved capacity of  $417 \text{ mA h g}^{-1}$ . Similarly, at a high current density of  $800 \text{ mA g}^{-1}$ , the RRGO-S@CF electrodes provide an initial discharge capacity of  $535 \text{ mA h g}^{-1}$  and deliver a capacity of  $390 \text{ mA h g}^{-1}$  even after 400 cycles with a capacity retention of 73% and 60% at the 500th cycle. The enhanced electrochemical performance is due to the graphene network and 3D-CF, which contributes to the electronic conductivity that accelerates the ion transfer process (fast reaction kinetics). The material provides a favorable interaction between the RRGO and lithium polysulfides, thus reducing the active material loss and polysulfide dissolution. The 3D-CF has an internal void space that offers good electrolyte infiltration, good Li-ion kinetics, and high sulfur utilization, alleviating the volume expansion. This approach demonstrates the construction of recycled materials from the spent LIBs as an inexpensive source to meet the growing energy demand in the practical development of LSBs.

## Data availability

The primary research works were carried out by us without using any public data. Some of the data supporting this article have been included as part of the ESI,† and are available upon reasonable request from the authors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Dr J. Priscilla Grace acknowledges DST-INSPIRE (code: IF 190016), Govt. of India, for the fellowship. Professor Surendra K. Martha acknowledges Greenco School of Sustainability, IIT Hyderabad, for the project Reference # GSS/IITH/02/2024-25/03 “Development and Realization of High Energy Lithium-based Rechargeable Batteries for Electric Vehicles” for financial support of the work. The authors thank Dr Madhushri Bhar for the valuable help with RRGO synthesis and Khamrul Islam Nadaf for help throughout the experiments.

## References

- 1 K. Zhu, C. Wang, Z. Chi, F. Ke, Y. Yang, A. Wang, W. Wang and L. Miao, *Front. Energy Res.*, 2019, 7, 123.
- 2 Z. Yang, J. Zhang, M. C. W. Kintner-Meyer, X. Lu, D. Choi, J. P. Lemmon and J. Liu, *Chem. Rev.*, 2011, 111, 3577–3613.
- 3 E. M. Erickson, F. Schipper, T. R. Penki, J.-Y. Shin, C. Erk, F.-F. Chesneau, B. Markovsky and D. Aurbach, *J. Electrochem. Soc.*, 2017, 164, A6341.
- 4 P. Slater and E. Kendrick, *J. Power Sources*, 2023, 588, 233710.
- 5 A. Manthiram, S.-H. Chung and C. Zu, *Adv. Mater.*, 2015, 27, 1980–2006.
- 6 L. Carbone, S. G. Greenbaum and J. Hassoun, *Sustainable Energy Fuels*, 2017, 1, 228–247.
- 7 D. Aurbach, *J. Electrochem. Soc.*, 2018, 165, Y1.
- 8 M. Zhao, B.-Q. Li, X.-Q. Zhang, J.-Q. Huang and Q. Zhang, *ACS Cent. Sci.*, 2020, 6, 1095–1104.
- 9 A. Manthiram, Y. Fu and Y.-S. Su, *Acc. Chem. Res.*, 2013, 46, 1125–1134.
- 10 D. Moy, A. Manivannan and S. R. Narayanan, *J. Electrochem. Soc.*, 2014, 162, A1.
- 11 F. Li, Q. Liu, J. Hu, Y. Feng, P. He and J. Ma, *Nanoscale*, 2019, 11, 15418–15439.
- 12 Y. Wang, R. Zhang, J. Chen, H. Wu, S. Lu, K. Wang, H. Li, C. J. Harris, K. Xi, R. V. Kumar and S. Ding, *Adv. Energy Mater.*, 2019, 9, 1900953.
- 13 Z. Ma, F. Jing, Y. Fan, J. Li, Y. Zhao and G. Shao, *J. Alloys Compd.*, 2019, 789, 71–79.
- 14 W. Jan, A. D. Khan, F. J. Iftikhar and G. Ali, *J. Energy Storage*, 2023, 108559.
- 15 X. Ji, K. T. Lee and L. F. Nazar, *Nat. Mater.*, 2009, 8, 500–506.
- 16 Y. Wang, B. Liu, W. Zhang, C. Shao, D. Lan, X. Qu, R. Chen, W. Zhang, W. Zhao, J. Liu, Y. Zhang and Z. Shi, *SN Appl. Sci.*, 2020, 2, 1276.
- 17 Z. Li, Y. Huang, L. Yuan, Z. Hao and Y. Huang, *Carbon*, 2015, 92, 41–63.
- 18 S. Evers and L. F. Nazar, *Acc. Chem. Res.*, 2013, 46, 1135–1143.



- 19 X. Gao, J. Li, D. Guan and C. Yuan, *ACS Appl. Mater. Interfaces*, 2014, **6**, 4154–4159.
- 20 T. Yang, J. Xia, Z. Piao, L. Yang, S. Zhang, Y. Xing and G. Zhou, *ACS Nano*, 2021, **15**, 13901–13923.
- 21 T. Long, F. Meng, B. Xu, Y. Zhao, W. Liu, X. Wei, L. Zheng and J. Liu, *Sustainable Energy Fuels*, 2020, **4**, 3926–3933.
- 22 Z. Zhu, Y. Zeng, Z. Pei, D. Luan, X. Wang and X. W. (David) Lou, *Angew. Chem., Int. Ed.*, 2023, **62**, e202305828.
- 23 W. Ahn, D. U. Lee, H. S. Song, S.-H. Yeon, K.-B. Kim and Z. Chen, *RSC Adv.*, 2015, **5**, 29370–29374.
- 24 M. Yu, R. Li, Y. Tong, Y. Li, C. Li, J.-D. Hong and G. Shi, *J. Mater. Chem. A*, 2015, **3**, 9609–9615.
- 25 M. Bhar, S. Ghosh, S. Krishnamurthy, Y. Kaliprasad and S. K. Martha, *RSC Sustainability*, 2023, **1**, 1150–1167.
- 26 U. Bhattacharjee, M. Bhar, S. Bhowmik and S. K. Martha, *Sustainable Energy Fuels*, 2023, **7**, 2104–2116.
- 27 S. Ghosh, M. Bhar, U. Bhattacharjee, K. Prasad Yalamanchili, S. Krishnamurthy and S. K. Martha, *J. Mater. Chem. A*, 2024, **12**, 11362–11377.
- 28 M. Bhar, U. Bhattacharjee, D. Sarma, S. Krishnamurthy, K. Yalamanchili, A. Mahata and S. K. Martha, *ACS Appl. Mater. Interfaces*, 2023, **15**, 26606–26618.
- 29 Y. Luo, F. Xu, L. Sun, Y. Xia, Y. Yao, Y. Guan, S. Fang, H. Hu, C. Zhang and R. Cheng, *J. Energy Storage*, 2024, **85**, 111067.
- 30 J. Wang, G. Yang, J. Chen, Y. Liu, Y. Wang, C. Lao, K. Xi, D. Yang, C. J. Harris, W. Yan, S. Ding and R. V. Kumar, *Adv. Energy Mater.*, 2019, **9**, 1902001.
- 31 Y. Zhao, Y. Zhang, Z. Bakenova and Z. Bakenov, *Front. Energy Res.*, 2015, **3**, 1–6.
- 32 Y. Hu, W. Chen, T. Lei, Y. Jiao, J. Huang, A. Hu, C. Gong, C. Yan, X. Wang and J. Xiong, *Adv. Energy Mater.*, 2020, **10**, 2000082.
- 33 K. Balakumar and N. Kalaiselvi, *RSC Adv.*, 2015, **5**, 34008–34018.
- 34 N. He, L. Zhong, M. Xiao, S. Wang, D. Han and Y. Meng, *Sci. Rep.*, 2016, **6**, 33871.
- 35 J. P. Grace, M. Bhar, S. Ghosh and S. K. Martha, *J. Alloys Compd.*, 2023, **969**, 172341.
- 36 J. P. Grace, S. Ghosh, M. Bhar and S. K. Martha, *J. Electrochem. Soc.*, 2024, **171**, 010509–010519.
- 37 S. Zhao, R. Fang, Z. Sun, S. Wang, J. Veder, M. Saunders, H. Cheng, C. Liu, S. P. Jiang and F. Li, *Small Methods*, 2018, **2**, 1800067.
- 38 W. S. Hummers and R. E. Offeman, *J. Am. Chem. Soc.*, 1958, **80**, 1339.
- 39 L. Qiang Lu, L. Jie Lu and Y. Wang, *J. Mater. Chem. A*, 2013, **1**, 9173–9181.
- 40 X. Yang, R. Li, J. Yang, H. Liu, T. Luo, X. Wang and L. Yang, *Carbon*, 2022, **199**, 215–223.
- 41 Q. Xu, Y. Wang, X. Shi, Y. Zhong, Z. Wu, Y. Song, G. Wang, Y. Liu, B. Zhong and X. Guo, *Green Chem.*, 2021, **23**, 942–950.
- 42 Z. Deng, L. Sun, Y. Sun, C. Luo, Q. Zhao and K. Yan, *RSC Adv.*, 2019, **9**, 32826–32832.
- 43 Y. Liu, M. Yao, L. Zhang and Z. Niu, *J. Energy Chem.*, 2019, **38**, 199–206.
- 44 S. Choudhury, M. Zeiger, P. Massuti-Ballester, S. Fleischmann, P. Formanek, L. Borchardt and V. Presser, *Sustainable Energy Fuels*, 2017, **1**, 84–94.
- 45 X. Liu, Z. Xiao, C. Lai, S. Zou, M. Zhang, K. Liu, Y. Yin, T. Liang and Z. Wu, *J. Mater. Sci. Technol.*, 2020, **48**, 84–91.
- 46 F. Xie, C. Xu, Y. Liang, Z. Tian, C. Ma, S. Xu, Z. Li, Z. U. Rehman and S. Yao, *J. Energy Storage*, 2023, **72**, 108712.
- 47 S. Ghosh, V. K. Kumar, S. K. Kumar, S. Biswas and S. K. Martha, *Electrochim. Acta*, 2019, **316**, 69–78.
- 48 H. Yu, M. Bi, C. Zhang, T. Zhang, X. Zhang, H. Liu, J. Mi, X. Shen and S. Yao, *Electrochim. Acta*, 2022, **428**, 140908.
- 49 L. Ji, M. Rao, H. Zheng, L. Zhang, Y. Li, W. Duan, J. Guo, E. J. Cairns and Y. Zhang, *J. Am. Chem. Soc.*, 2011, **133**, 18522–18525.

