


 Cite this: *Chem. Commun.*, 2026, 62, 2568

 Received 16th October 2025,  
 Accepted 15th December 2025

DOI: 10.1039/d5cc05916j

[rsc.li/chemcomm](https://rsc.li/chemcomm)

# Atom-efficient iron-catalyzed cascade synthesis of pyrroles from nitroarenes under low-pressure conditions

 Germán López Robledo,<sup>†</sup> Johannes Fessler,<sup>†</sup> Kathrin Junge<sup>†\*</sup> and Matthias Beller<sup>†\*</sup>

**Conventional pyrrole syntheses typically rely on multistep procedures or pre-functionalized substrates. Here, we report a one-pot Paal–Knorr cascade reaction that directly converts nitroarenes into pyrroles. Employing low-pressure hydrogenation in the presence of an iron catalyst, this approach enhances atom economy and sustainability, offering an efficient and environmentally benign alternative to traditional methods.**

Pyrroles are key structural motifs present in a diverse array of natural products,<sup>1</sup> pharmaceuticals,<sup>2,3</sup> and functional materials.<sup>4–6</sup> Since its discovery in 1885, the Paal–Knorr reaction, the acid-catalyzed condensation of 1,4-dicarbonyl compounds with primary amines, has remained a cornerstone in the synthesis of substituted pyrroles.<sup>7,8</sup> Subsequent refinements have expanded its scope through modified conditions and alternative substrates.<sup>9</sup> Nevertheless, traditional pyrrole syntheses frequently rely on multistep sequences or pre-functionalized starting materials,<sup>10</sup> which can undermine their overall efficiency, practicality, and sustainability.


In this context, nitroarenes represent attractive starting materials due to their wide availability, low cost, and greater stability compared to the corresponding anilines.<sup>11–13</sup> Accordingly, their direct conversion into pyrroles could significantly streamline synthetic routes, provided that mild and chemoselective reduction strategies are available. Among existing reduction methodologies, catalytic hydrogenation using molecular hydrogen (H<sub>2</sub>) is particularly appealing, offering excellent atom economy and producing only water as a byproduct. However, conventional hydrogenation protocols typically rely on precious metal catalysts and/or require high H<sub>2</sub> pressures and elevated temperatures,<sup>14</sup> often compromising functional group tolerance and sustainability.

To address these limitations, growing interest has focused on developing selective catalytic systems based on earth-abundant


metals, which offer a more sustainable and cost-effective alternative to precious metal catalysts.<sup>15</sup> In parallel, the rising demand for greener synthetic methodologies has catalyzed the adoption of cascade strategies, which integrate multiple bond-forming events into a single operational step.<sup>16,17</sup> Such approaches improve atom economy, reduce solvent use and waste, and streamline purification processes.

In this regard, a cascade strategy offers an attractive approach for converting nitroarenes to pyrroles *via* the Paal–Knorr reaction, as it combines selective nitroarene reduction with condensation–cyclization in a single operation, providing a sustainable and atom-efficient alternative to conventional multistep routes (Scheme 1A).


A) Cascade Paal–Knorr synthesis of pyrroles from nitroarenes

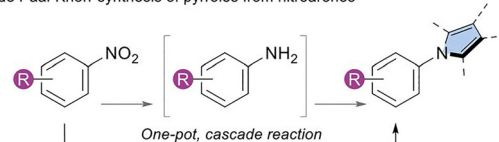

B) First homogeneous Fe-catalyzed cascade pyrrole synthesis

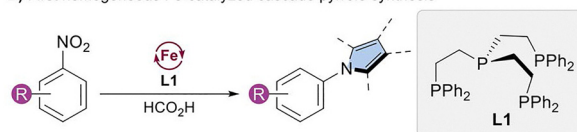

C) **This work:** mild and homogeneous cascade pyrrole synthesis

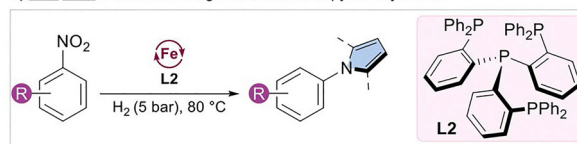

- ✓ Green reductant (H<sub>2</sub>)
- ✓ Earth-abundant metal (Fe)
- ✓ Cascade, one-pot reaction
- ✓ Mild conditions (5 bar, 80 °C)
- ✓ Good functional group tolerance
- ✓ Moderate to excellent yields (93%)

**Scheme 1** Recent developments in homogeneous Fe-catalyzed cascade syntheses of pyrroles from nitroarenes: (A) Paal–Knorr cascade *via* aniline intermediates; (B) first homogeneous Fe-catalyzed example; (C) this work: homogeneous cascade synthesis under low-pressure hydrogenation.

Leibniz-Institute für Katalyse e.V., Albert-Einstein-Straße 29a, 18059 Rostock, Germany. E-mail: [kathrin.junge@catalysis.de](mailto:kathrin.junge@catalysis.de), [matthias.beller@catalysis.de](mailto:matthias.beller@catalysis.de)



While several cascade syntheses of pyrroles from nitroarenes *via* the Paal–Knorr reaction have been reported in the past, most rely on heterogeneous catalysts.<sup>18–23</sup> Recently, we described the first homogenous non-noble metal catalytic procedure for this transformation (Scheme 1B).<sup>24</sup> Shortly after, an alternative approach using a molybdenum catalyst was also described.<sup>25</sup> In our previous work, we discovered that the combination of an iron (Fe) precursor with the phosphorous-based ligand tetrphos (tris(2-(diphenylphosphino)ethyl)phosphine) (**L1**) enabled the efficient reductive condensation of nitroarenes with 1,4-dicarbonyl compounds. While formic acid was selected as the primary hydrogen donor, other hydrogenation conditions were briefly explored, showing limited success across a small set of substrates.

Building on these developments and recognizing the advantages of molecular hydrogen as a clean and atom-efficient reductant, we sought to optimize this transformation, offering a more sustainable approach to pyrrole synthesis. Herein, we report a homogeneous, one-pot, cascade reduction-condensation strategy for the synthesis of pyrroles from nitroarenes and 2,5-hexanedione under low-pressure hydrogenation conditions (Scheme 1C). The method exhibits broad functional group tolerance and provides various substituted pyrroles in good to excellent yields (up to 93%).

Guided by our previous results with the Ph-tetrphos (tris(2-(diphenylphosphino)phenyl)phosphine) (**L2**) system,<sup>26</sup> we conducted a preliminary evaluation of a series of structurally related ligands, selecting nitrobenzene as the model substrate, 2,5-hexanedione as the 1,4-dicarbonyl compound, and Fe(BF<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O as the Fe source (Table 1, entries 1–4). Compared to the

unmodified ligand, the introduction of an electron-donating group (**L3**) proved slightly detrimental to the reaction, whereas the incorporation of an electron-withdrawing group (**L4**) resulted in a significant decrease in catalytic activity. Increasing the steric bulk of the ligand (**L5**) also led to a pronounced negative effect. Ultimately, the initial system outperformed all modified variants, which can be rationalized by considering the steric hindrance associated with the ligand modifications (Ph < 4-MeO-Ph < 4-CF<sub>3</sub>-Ph < Xylyl).

Having identified the optimal ligand for the transformation, we next examined the influence of different Lewis acids. The results of this extensive evaluation—which included sulfonamides, sulfonic acids, mineral acids, halogenated acids, and other common acids—are presented in the SI (Fig. S1 and Table S1). Among the acids tested, the highest yields were obtained with fluorinated analogues such as heptafluorobutyric acid (69%), chlorodifluoroacetic acid (74%), and trifluoroacetic acid (TFA, 98%). Interestingly, no product formation was observed when trichloroacetic acid was used. Attempts employing strong mineral acids, non-halogenated carboxylic acids, or sulfonamides resulted only in poor conversions.


Given the increasing regulatory restrictions on polyfluorinated compounds,<sup>27</sup> and aiming for a greener and more sustainable approach, we investigated the effect of acid concentration in a series of sulfonic acids, as they were the second-best performing group (up to 18%) (Fig. S2). This analysis revealed that each acid—as well as TFA—exhibits optimal performance within a narrow and well-defined concentration (pH) range. Although comparably higher yields could be achieved (up to 41% for camphorsulfonic acid), these values remained significantly lower than those obtained with TFA (98%). For this reason, TFA was selected for use in subsequent experiments.

Next, the influence of the solvent was evaluated (Table 1, entries 5–14). Polar solvents such as *i*-PrOH, 2-butanol, and 2-pentanol, along with THF, provided the best yields. In contrast, product formation was significantly reduced when the reaction was carried out in non-polar solvents such as toluene and cyclohexane. An extended list can be found in Table S2. Since THF proved to be more robust than 2-pentanol, it was selected as the preferred solvent.

Following this analysis, we explored the effect of other variables on the reaction outcome. The main results are summarized in Table 2. Replacing the original Fe precursor with Fe(acac)<sub>2</sub> (Table 2, entry 2) or Fe(OAc)<sub>2</sub> (Table 2, entry 3) led to comparable results. In contrast, no product formation was observed when FeBr<sub>2</sub> and FeCl<sub>2</sub> were used (Table 2, entry 4). Increasing the amount of 2,5-hexanedione (Table 2, entry 5) did not evidence any significant improvement. The addition of molecular sieves to the reaction mixture (Table 2, entry 6) proved detrimental to product formation. Increasing the reaction time to 6 hours led to full conversion and 85% product yield (Table 2, entry 7).

Aiming to achieve the desired transformation under milder conditions, reactions were performed at 80 °C (Table 2, entry 8) and 60 °C (Table 2, entry 9) with extended reaction times. While 80 °C afforded very good yields, the reaction at 60 °C failed to

**Table 1** Screening of ligands and solvents in the cascade synthesis of pyrroles from nitroarenes

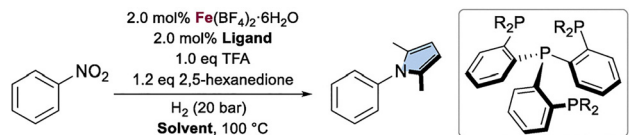

Entry	Ligand	Solvent	Yield [%]
1 <sup>a</sup>	<b>L2</b> : R = Ph		84
2 <sup>a</sup>	<b>L3</b> : R = 4-MeO-Ph	THF	70
3 <sup>a</sup>	<b>L4</b> : R = 4-CF <sub>3</sub> -Ph		38
4 <sup>a</sup>	<b>L5</b> : R = Xylyl		27
5 <sup>b</sup>		THF	71
6 <sup>b</sup>		1,4-Dioxane	19
7 <sup>b</sup>		EtOH	38
8 <sup>b</sup>		<i>i</i> -PrOH	64
9 <sup>b</sup>		<i>t</i> -AmOH	58
10 <sup>b</sup>	<b>L2</b>	2-Butanol	66
11 <sup>b</sup>		2-Pentanol	72
12 <sup>b</sup>		Dibutyl ether	< 5
13 <sup>b</sup>		Toluene	< 5
14 <sup>b</sup>		Cyclohexane	< 5

Reaction conditions: Fe(BF<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.01 mmol, 2.0 mol%), ligand (0.01 mmol, 2.0 mol%), TFA (0.5 mmol, 1.0 equiv.), nitrobenzene (0.5 mmol, 1.0 equiv.), 2,5-hexanedione (0.6 mmol, 1.2 equiv.), solvent (1.5 mL), H<sub>2</sub> (20 bar), 100 °C. <sup>a</sup> 2 h. <sup>b</sup> 1 h. Yields were determined by GC-FID analysis using hexadecane as internal standard. *t*-AmOH: 2-methyl-2-butanol.




Table 2 Further optimization of the reaction conditions

Entry	Deviation from standard conditions	Yield [%]
1	None	59
2	Fe(acac) <sub>2</sub> as Fe precursor	52
3	Fe(OAc) <sub>2</sub> as Fe precursor	55
4	FeCl <sub>2</sub> or FeBr <sub>2</sub> as Fe precursor	0
5	1.5 equiv. 2,5-hexanedione	58
6	3 Å molecular sieves	35
7	Reaction time: 6 h	85
8	80 °C, 18 h	83
9	60 °C, 24 h	66
10	80 °C, 18 h, 1.5 mol% catalyst	76
11	5 bar H <sub>2</sub> , 80 °C, 18 h, 0.35 equiv. TFA	93

Standard conditions: Fe(BF<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.01 mmol, 2.0 mol%), L2 (0.01 mmol, 2.0 mol%), TFA (0.5 mmol, 1.0 equiv.), nitrobenzene (0.5 mmol, 1.0 equiv.), 2,5-hexanedione (0.6 mmol, 1.2 equiv.), THF (1.5 mL), H<sub>2</sub> (20 bar), 100 °C, 1 h. Yields were determined by NMR analysis using 1,3,5-trimethoxybenzene as internal standard.

deliver comparable results. Attempts to further reduce the catalyst loading (Table 2, entry 10) also proved unsuccessful. Extended optimization allowed the use of low H<sub>2</sub> pressures (5 bar) and reduced TFA loadings (0.35 equiv.) (Table 2, entry 11), which were ultimately selected as the optimized conditions.

With the optimized conditions in hand, we proceeded to evaluate the general applicability of the system (Scheme 2). The reaction of the model substrate (**1a**) afforded the product in excellent yield (92%). The introduction of a methyl group at the *ortho* position (**2a**) led to a pronounced drop in yield (30%), likely due to steric hindrance affecting catalyst coordination. Given the pronounced effect of acid concentration on the reaction outcome, the reaction was repeated using an increased amount of TFA (1.0 equiv.). Under these conditions, the product was isolated in 62% yield, further highlighting the critical role of pH in this transformation. Nitrobenzenes bearing electron-donating groups such as -OH (**3a**) and -OMe (**4a**) afforded the desired product in excellent and very good yields, respectively. Notably, sulfur-containing nitroarene **5a**, which is known to poison Pd/C during hydrogenation,<sup>28</sup> was successfully converted under the present conditions. In general, halogen derivatives (**6a–9a**) were well tolerated, and no side-products were observed. The reaction also proceeded smoothly in the presence of boronic ester **10a**, furnishing the corresponding pyrrole in 70% yield. When an olefin-containing substrate was tested (**11a**), moderate product formation was observed; importantly, no over-reduction was detected. An alkynyl-nitroarene, 1-ethynyl-4-nitrobenzene (see SI), was detected in 26% yield. However, under the reaction conditions both the starting material and the corresponding pyrrole were not well tolerated and underwent reduction to the respective alkenes and/or hydration products, leading to an overall conversion of 51%. The nitrile-substituted nitroarene (**12a**) resulted in a poor conversion, likely due to the strong electron-withdrawing nature of the

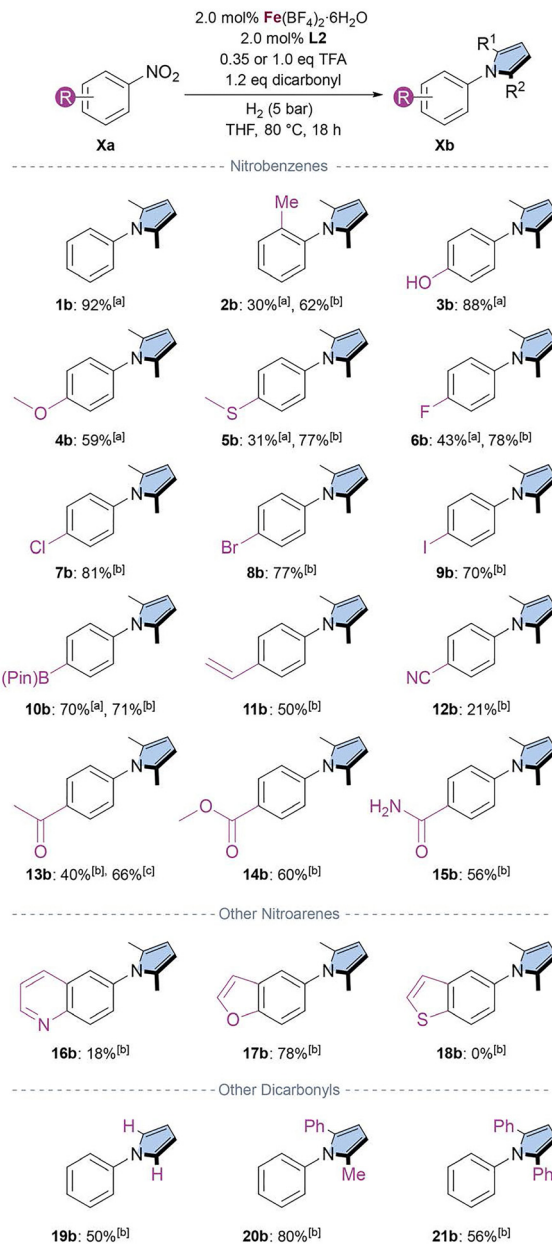

**Scheme 2** Substrate scope for the cascade synthesis of pyrroles from nitroarenes. Reaction conditions: <sup>a</sup> Fe(BF<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.01 mmol, 2.0 mol%), L2 (0.01 mmol, 2.0 mol%), TFA (0.175 mmol, 0.35 equiv.), nitrobenzene (0.5 mmol, 1.0 equiv.), dicarbonyl (0.6 mmol, 1.2 equiv.), THF (1.5 mL), H<sub>2</sub> (5 bar), 80 °C, 18 h; <sup>b</sup> TFA (0.5 mmol, 1.0 equiv.); <sup>c</sup> Fe(BF<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.025 mmol, 5.0 mol%), L2 (0.025 mmol, 5.0 mol%). Isolated yields are shown.

nitrile group, which may hinder reduction, or due to catalyst inhibition.

We next examined acyl-substituted nitrobenzenes (**13a–15a**), which generally afforded moderate yields (40–60%). Here, higher yields were obtained when substrate **13a** was tested at an increased catalyst loading (from 40% to 66%). Similar improvements are likely achievable for other low-yielding substrates, although higher catalyst loadings would be required. Notably, an aldehyde-containing substrate, 4-nitrobenzaldehyde (see SI) failed to react, and no product formation was detected.



To further assess the scope of the methodology, three nitroarenes bearing heterocycles were evaluated. Nitrogen-containing heteroarenes, such as 6-nitroquinoline (**16a**), were not tolerated under the reaction conditions (18% yield). A similar behavior was observed for 3-nitropyrrole, which showed approximately 20% conversion by GC-FID analysis (see SI). In contrast, 5-nitrobenzofuran (**17a**) afforded the desired pyrrole in 78% yield. Notably, the sulfur-containing heterocycle 5-nitrobenzo[*b*]thiophene (**18a**) was not reduced.

Finally, we examined the reaction when 2,5-hexanedione was replaced with other dicarbonyl sources. Using 2,5-dimethoxytetrahydrofuran as a succinaldehyde surrogate (**19a**) afforded moderate yields of the corresponding pyrrole (50%). The reaction with 1-phenylpentane-1,4-dione (**20a**) provided very good yields (80%), whereas a more challenging dicarbonyl, 1,4-diphenylbutane-1,4-dione (**21a**), gave moderate yields (56%). Overall, the scope and limitations of the reaction across diverse nitroarene substrates and dicarbonyl sources were evaluated.

In summary, we have developed an atom-economical cascade synthesis of pyrroles directly from nitroarenes. Using an iron-based catalyst in combination with a phosphine ligand, the transformation proceeds under mild conditions and low hydrogen pressure, delivering pyrroles in good to excellent yields. This sustainable protocol demonstrates comparable efficiency to our previous methodology while offering improved potential for industrial implementation.

GLR: conceptualization, methodology, validation, investigation, writing – original draft, writing – review & editing, visualization. JF: conceptualization, methodology, validation, investigation, writing – review & editing. KJ: writing – review & editing, supervision, project administration, funding acquisition. MB: writing – review & editing, supervision, project administration, funding acquisition.

## Conflicts of interest

There are no conflicts to declare.

## Data availability

The data supporting this article have been included as part of the supplementary information (SI). Supplementary information is available. See DOI: <https://doi.org/10.1039/d5cc05916j>.

## Acknowledgements

The authors thank PD Dr Wolfgang Baumann and Susann Buchholz for NMR measurements. GLR is also grateful to Dr

Rafal Kusy, Sebastian Ahrens, Faral Akhtar, and Fairroosa Poovan for proofreading and valuable discussions.

## References

- 1 N. Singh, S. Singh, S. Kohli, A. Singh, H. Asiki, G. Rathee, R. Chandra and E. A. Anderson, *Org. Chem. Front.*, 2021, **8**, 5550–5573.
- 2 B. H. Ganesh, A. G. Raj, B. Aruchamy, P. Nanjan, C. Drago and P. Ramani, *ChemMedChem*, 2024, **19**, e202300447.
- 3 G. Li Petri, V. Spano, R. Spatola, R. Holl, M. V. Raimondi, P. Barraja and A. Montalbano, *Eur. J. Med. Chem.*, 2020, **208**, 112783.
- 4 M. Krzeszewski, D. Gryko and D. T. Gryko, *Acc. Chem. Res.*, 2017, **50**, 2334–2345.
- 5 Y. Liu and F. Wu, *Nanoscale Adv.*, 2023, **5**, 3606–3618.
- 6 A. Deronzier and J. C. Moutet, *Acc. Chem. Res.*, 1989, **22**, 249–255.
- 7 C. Paal, *Ber. Dtsch. Chem. Ges.*, 1885, **18**, 367–371.
- 8 L. Knorr, *Ber. Dtsch. Chem. Ges.*, 1885, **18**, 299–311.
- 9 J. Li, J. Sun, Y. Wang, J. Liu and H. Cheng, *ACS Sustainable Chem. Eng.*, 2024, **13**, 571–582.
- 10 V. Bhardwaj, D. Gumber, V. Abbot, S. Dhiman and P. Sharma, *RSC Adv.*, 2015, **5**, 15233–15266.
- 11 M. Orlandi, D. Brenna, R. Harms, S. Jost and M. Benaglia, *Org. Process Res. Dev.*, 2016, **22**, 430–445.
- 12 C. W. Cheung, M. Leendert Ploeger and X. Hu, *Chem. Sci.*, 2018, **9**, 655–659.
- 13 A. Capperucci, M. Clemente, A. Cenni and D. Tanini, *ChemSusChem*, 2023, **16**, e202300086.
- 14 D. Formenti, F. Ferretti, F. K. Scharnagl and M. Beller, *Chem. Rev.*, 2019, **119**, 2611–2680.
- 15 V. Zubar, A. Dewanji and M. Rueping, *Org. Lett.*, 2021, **23**, 2742–2747.
- 16 E. S. Beach, Z. Cui and P. T. Anastas, *Energy Environ. Sci.*, 2009, **2**, 1038–1049.
- 17 K. C. Nicolaou, D. J. Edmonds and P. G. Bulger, *Angew. Chem., Int. Ed.*, 2006, **45**, 7134–7186.
- 18 Y. Lin, F. Wang, E. Ren, F. Zhu, Q. Zhang and G.-P. Lu, *J. Catal.*, 2022, **416**, 39–46.
- 19 P. Ryabchuk, T. Leischner, C. Kreyenschulte, A. Spannenberg, K. Junge and M. Beller, *Angew. Chem., Int. Ed.*, 2020, **59**, 18679–18685.
- 20 Z. Gong, Y. Lei, P. Zhou and Z. H. Zhang, *New J. Chem.*, 2017, **41**, 10613–10618.
- 21 A. Serrano-Maldonado, E. Martin and I. Guerrero-Ríos, *Eur. J. Inorg. Chem.*, 2019, 2863–2870.
- 22 X. Yu, M. Miao, S. Huo, X. Tang, L. Ni, S. Liu and L. Wang, *ACS Appl. Mater. Interfaces*, 2024, **16**, 16363–16372.
- 23 J. Luis del Río-Rodríguez, A. Tiscareño-Ferrer, S. Gutiérrez-Tarriño and P. Oña-Burgos, *ChemCatChem*, 2025, **17**(22), e00811.
- 24 J. Fessler, K. Junge and M. Beller, *Chem. Sci.*, 2023, **14**, 11374–11380.
- 25 S. Gómez-Gil, S. Suárez-Pantiga, M. R. Pedrosa and R. Sanz, *Adv. Synth. Catal.*, 2024, **367**, e202401170.
- 26 G. Wienhofer, M. Baseda-Kruger, C. Ziebart, F. A. Westerhaus, W. Baumann, R. Jackstell, K. Junge and M. Beller, *Chem. Commun.*, 2013, **49**, 9089–9091.
- 27 J. C. DeWitt, J. Gluge, I. T. Cousins, G. Goldenman, D. Herzke, R. Lohmann, M. Miller, C. A. Ng, S. Patton, X. Trier, L. Vierke, Z. Wang, S. Adu-Kumi, S. Balan, A. M. Buser, T. Fletcher, L. S. Haug, A. Heggelund, J. Huang, S. Kaserzon, J. Leonel, I. Sheriff, Y. L. Shi, S. Valsecchi and M. Scheringer, *Environ. Sci. Technol. Lett.*, 2024, **11**, 786–797.
- 28 R. Xiong, W. Ren, Z. Wang and M. Zhang, *ChemCatChem*, 2020, **13**, 548–552.

