


 Cite this: *Chem. Commun.*, 2026, 62, 2374

Silver clusters embedded within zeolites for innovative (bio)sensing platforms

 Cecilia García-Guzmán,^a Stefano Cinti,^b Eduardo Coutino-Gonzalez^{c,e} and Eden Morales-Narváez^{d,f}

Silver clusters embedded within zeolites combine the molecular-like optical and electrochemical properties of sub-nanometric clusters with the structural robustness, porosity, and ion-exchange capacity of crystalline frameworks. Their unique features, such as tunable emission with high quantum yields, large Stokes shifts, redox activity, electrocatalytic behavior, and sensitivity to external stimuli, enable versatile sensing capabilities. These composites have already demonstrated remarkable versatility, enabling optical detection of water vapor, volatile amines, oxygen, and biomolecules, as well as electrochemical sensing of hydrogen peroxide, tryptophan, and chloride ions. Their integration into immunosensors, optical hydration switches, and electrochemical paper-based strips highlights their disruptive potential for portable and wearable devices. However, key challenges remain, including controlled nucleation, tailoring excitation–emission properties, and ensuring stability after biorecognition functionalization and device integration. This review discusses the structure–property relationships that govern the optical and electrochemical responses of silver clusters embedded within zeolites, summarizes recent advances in (bio)sensing applications, and outlines the challenges that must be overcome for their translation into scalable, robust, and sustainable devices. With continued progress in material design, surface functionalization, and integration within microfluidic and data analysis platforms, silver cluster–zeolite composites hold strong promise to evolve from laboratory prototypes into portable technologies for diagnostics and environmental monitoring, displaying significant promises for next-generation point-of-care and wearable sensors.

 Received 28th October 2025,
 Accepted 18th December 2025

DOI: 10.1039/d5cc06135k

rsc.li/chemcomm

Introduction

Next-generation (bio)sensing platforms are redefining how we detect biomolecules and environmental contaminants, aiming for high stability, sensitivity, and selectivity in cost-effective and sustainable formats. The integration of functional materials with exceptional photophysical and electrochemical properties is central to this progress, which enables conceptually innovative (bio)sensing platforms.¹ Among the strategies driving this transformation, silver clusters have

emerged as versatile functional materials that combine unique optical and electrochemical properties with tunable chemical interactions.^{2,3}

These clusters have enabled innovative sensing approaches that were previously difficult to achieve. For instance, DNA-templated silver clusters can be used to detect cancer-associated miRNAs, such as miRNA-21, in human serum at nanomolar concentrations using fluorescence resonance energy transfer (FRET), offering a minimally invasive route for early disease detection.⁴ Similarly, polyethyleneimine-stabilized silver clusters allow rapid, colorimetric and fluorometric detection of metabolites such as ascorbic acid directly in urine, demonstrating the potential for point-of-care diagnostics.⁵ Silver clusters have also been applied in environmental monitoring, achieving micromolar detection limits for metal ions like Cu²⁺, Ni²⁺, and Fe²⁺ in tap and wastewater, providing rapid and practical tools for public health and ecological safety.⁶ Besides, the integration of silver clusters into portable devices and wearable sensors represents a potential breakthrough in the field of biosensors. To achieve this, new host templates have been explored to enhance stability and facilitate their incorporation into portable devices. Building on these

^a Centro de Investigaciones en Óptica (CIO), A. C., Loma Del Bosque 115, Lomas Del Campestre, León, 37150, Guanajuato, Mexico

^b Department of Pharmacy, University of Naples “Federico II”, 80131, Naples, Italy. E-mail: stefano.cinti@unina.it

^c Sbarro Institute for Cancer Research and Molecular Medicine, Center for Biotechnology, College of Science and Technology, Temple University, Philadelphia, PA, 19122, USA

^d Bioelectronics Task Force at University of Naples Federico II, Via Cinthia 21, Naples, 80126, Italy

^e Interuniversity Microelectronics Center (IMEC), Kapeldreef 75, 3001, Leuven, Belgium. E-mail: eduardo.coutinogonzalez@imec.be

^f Universidad Nacional Autónoma de México, Centro de Física Aplicada y Tecnología Avanzada, Querétaro, 76230, Mexico. E-mail: eden@fata.unam.mx



Highlight


concepts, silver clusters confined into inorganic templates, such as zeolites, have demonstrated remarkable (bio)sensing potential, offering improved stability, high luminescence quantum yields, electrical conductivity, biocompatibility, and facile surface functionalization. Moreover, zeolite-supported silver clusters can respond sensitively to external stimuli, with detectable luminescence changes enabling wash-free, rapid, and cost-effective analyte detection,^{1,7} positioning zeolite-confined silver clusters on organic and inorganic templates such as DNA, polymers and metal organic frameworks (MOFs), among others.

Compared with other nanomaterials commonly used for (bio)sensing, such as gold nanoparticles⁸ and semiconductor quantum dots,⁹ silver clusters stand out for their sub-nanometric dimensions, molecular-like electronic structure, and biocompatibility.¹⁰ Their small size minimizes cytotoxicity and enables interaction with biomolecules at the molecular level, while their discrete energy levels confer tunable luminescence and redox properties not attainable in larger nanoparticles.¹¹ Furthermore, when confined within zeolites, these clusters exhibit remarkable stability against aggregation and photobleaching, ensuring long-term operation under physiological and environmental conditions.¹²

Herein, we highlight recent advances in the optical and electrochemical properties of silver clusters stabilized in zeolite templates, discussing how zeolite frameworks stabilize and modulate these properties. A particular emphasis is made on their structure–property relationships and implications for (bio)sensing. Then, recent advances in chemical sensing, biosensing and the integration of silver–cluster zeolite composites into portable optical and electrochemical devices are highlighted. Finally, the challenges and opportunities associated with the integration of these materials into portable, robust, selective and sustainable biosensing devices are presented, offering a forward-looking view on their potential to transform healthcare diagnostics and environmental monitoring.

Sub-nanometric silver clusters in zeolites: structure, properties, and implications for (bio)sensing

Sub-nanometric silver clusters (<2 nm), composed of a few to several hundred atoms, exhibit molecular-like behavior due to their size being comparable to the Fermi wavelength. Their conduction and valence bands consist of discrete energy levels separated by a band gap,¹³ endowing them with unique physical and chemical properties such as electrocatalytic activity,⁷ photoluminescence with large Stokes shifts,¹⁴ tunable

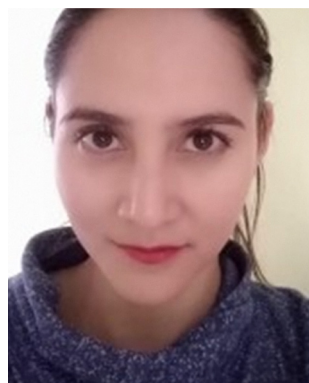

Cecilia García-Guzmán

Cecilia García-Guzmán is a Pharmaceutical Chemist Biologist (QFB) from the University of Guanajuato (Mexico). She obtained her Master's degree in Optical Sciences from the Center for Research in Optics (CIO, Mexico), where she is currently completing her PhD in Optical Sciences under the supervision of Dr Eden Morales and Dr Eduardo Coutino. Her doctoral research is focused on biosensing strategies based on silver clusters confined

within zeolite composites, combining optical and electrochemical transduction approaches. Her work includes the development and characterization of portable sensing platforms for analytical and biomedical applications. During her PhD, she carried out a research stay at the University of Naples Federico II (Italy) under the supervision of Dr Stefano Cinti.



Stefano Cinti

Prof. Stefano Cinti leads the UniNanoBiosensors Lab (uninanosensors.com) at the University of Naples Federico II, and his research interests include the development of electrochemical sensors, portable diagnostics, paper-based devices and nanomaterials. During his research activity, he had the opportunity to spend a period abroad in Finland, the U.K., the U.S., Germany, and Spain. He has published more than 150

papers in peer-reviewed journals, with an H-index of 45 and >7500 citations. Among all the prizes and certificates, in 2018 he was named Best Young Researcher in Bio-Analytical Chemistry, in 2019 he was named Best Young Researcher in Analytical Chemistry (both by the Italian Chemical Society), in 2022 he was awarded with the early career award from the International Society of Electrochemistry in Analytical Electrochemistry, in 2022 he was awarded with the Biosensors 2022 Young Investigator Award, in 2023 he received the Sensor Division Early Career Award from the Electrochemical Society (ECS), in 2024 he was included in the ACS Measurement Science Au Rising Stars, and from 2021 has been regularly included in the World's Top 2% Scientists. He is the Chair of AMYC-BIOMED, a multidisciplinary conference for young chemists in the biomedical sciences. He is very active in communicating science to nonspecialized audiences through TV shows, radio, and magazines.



emission¹⁵ and responsiveness to environmental stimuli,¹⁶ making them highly attractive for (bio)sensing applications. These clusters are often referred to as “super-atoms” due to their high symmetry, super-atomic orbitals, and predictable electronic structures in the gas phase, where environmental perturbations are minimized. Their physicochemical properties include high conductivity and strong photoluminescence.^{17,18} Importantly, these properties are size-dependent; smaller clusters (subnanometer to 1–2 nm) exhibit enhanced surface reactivity and catalytic potential, while larger clusters (few to several nanometers) offer greater thermodynamic stability and bonding energy.¹⁹ Theoretical and experimental studies have predicted optimal crystal structures and orbital configurations, driving research into how these parameters influence cluster behavior.^{20–22}

However, due to their high surface energy and environmental reactivity, metallic clusters tend to aggregate into nanoparticles. To prevent this, stabilization strategies involving protective ligands or templates are commonly employed.²³ Among inorganic templates, zeolites stand out for their

structural and chemical versatility. Zeolites are three-dimensional aluminosilicate frameworks composed of tetrahedral units, where partial substitution of Si⁴⁺ by Al³⁺ generates a negative framework charge balanced by extra-framework cations such as Na⁺, K⁺, and Ca²⁺, among other monovalent and divalent cations.²⁴ The Si/Al ratio governs key properties including reactivity and hydrophilicity.²⁵ Variations in the crystal structure and pore size, determined by the arrangement of tetrahedral units, enable the stabilization of diverse subnanometric metallic clusters.^{24,26} Cluster size and type are influenced by the dimensions of the crystalline cavities, atomic arrangement within the framework, and the exchange affinity of the extra-framework cations.²⁷ Furthermore, zeolite porosity acts as a molecular sieve, imparting selectivity and enabling targeted interactions with analytes based on size and chemical properties.


To date, ion exchange remains the most widely used method for synthesizing silver clusters in zeolites and other inorganic frameworks, owing to its simplicity and cost-effectiveness. In this approach, natural or synthetic zeolites are suspended in a



Eduardo Coutino-Gonzalez

Dr Eduardo Coutino-Gonzalez is an R&D Project Manager at IMEC (Belgium). He earned his PhD in Chemistry from KU Leuven (2015), focusing on nanostructured luminescent materials formed by self-assembly in confined spaces. He subsequently worked at CIDETEQ and later as a Principal Researcher at CIO (Mexico), leading the Nanophotonics Laboratory, before joining VITO (Belgium) as a Research Scientist in sustainable

advanced materials. His interdisciplinary work spans photochemistry, nanophotonics and sustainable materials, including pioneering studies on subnanometer silver clusters.

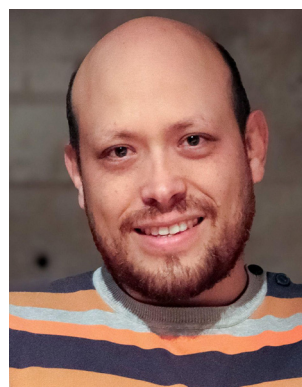

Eden Morales-Narváez

Prof. Eden Morales-Narváez is currently the Head of the Biophotonic Nanosensors Laboratory at the Center for Applied Physics and Advanced Technology of the National Autonomous University of Mexico (Universidad Nacional Autónoma de México, UNAM). He received a degree in bionics engineering from the National Polytechnic Institute of Mexico in 2006 and his PhD in biomedical engineering from the

Polytechnic University of Catalonia, Spain in 2013. He was a Postdoctoral Researcher at the Catalan Institute of Nanoscience and Nanotechnology and started his independent career in late 2016 at the Center for Research in Optics (Mexico). His research is focused on the development and application of novel (bio)sensing platforms, particularly using nanophotonics at the cutting-edge. In general, he is interested in green technologies, smart materials, integrated biosensors, wearable devices, flexible photonics, and healthcare 4.0/5.0. He is a member of several editorial boards including JPhys: Photonics, ACS Analytical Chemistry, Biosensors & Bioelectronics X and Green Analytical Chemistry, among others. As a winner of the 2020 JPhys Photonics Early Career Award, he has also been recognized as an Emerging Leader. He was also selected as a 2023 Rising Star by ACS Measurement Science Au. Eden is also a recipient of the “Cátedra Marcos Moshinsky 2024”, which is awarded to the most prominent young scientist in Mexico. Listed as a top-cited scientist in the field of Analytical Chemistry/ Nanoscience and Nanotechnology, Eden also earned a place in the Stanford–Elsevier rankings.



Highlight

silver cation solution, enabling the exchange of extra-framework cations (e.g., Na⁺, K⁺, Ca²⁺, and Mg²⁺) through competitive affinity. Subsequent reduction of the silver ions, *via* thermal treatment,²⁸ UV irradiation,²⁹ or X-ray exposure,³⁰ yields silver clusters with high quantum yields and notable catalytic activity. However, this method offers limited control over cluster size, as the ion-exchange capacity restricts silver incorporation, leading to preferential formation in superficial zeolite cavities.

Optoelectrochemical properties of silver clusters in zeolites: dynamics, modulation, and sensing potential

Silver clusters, owing to quantum confinement and molecular-like behavior, exhibit a rich array of optical and electrochemical properties, including multiple absorption bands, photoluminescence, and charge transfer.²¹ Their excited-state dynamics span from femtoseconds to milliseconds, with interactions in the surrounding media playing a critical role in shaping electronic states.³¹

Photoluminescence arises from transitions such as d-orbital excitations at shorter wavelengths and s → p transitions at longer wavelengths, depending on the cluster's net charge. Upon photon absorption, relaxation occurs *via* several pathways: ultrafast decay (fs–ps) through internal conversion and vibrational relaxation; intermediate decay (ps–ns) from emissive states; and long-lived decay (μs–ms) involving intersystem crossing, electron–hole recombination, or trap states.^{31–33}

The local electronic environment strongly influences inter-system crossing, particularly through overlap between the triplet and P-type singlet states.^{16,31} Water molecules coordinated within the zeolite framework and nearby atoms enhance luminescence by generating degenerate singlet and triplet excited states.^{34,35} Water molecules within the zeolite cavities play a central role in modulating emission behavior, either enhancing or quenching luminescence depending on their coordination to the clusters. Controlled dehydration, achieved through thermal treatment, or exclusion by small cations such

as Li⁺, which hinder cavity entry, can shift emission wavelengths and modify luminescence lifetimes by altering electrostatic fields and electronic coupling between cluster atoms and degenerate states.^{32,36} Silver atoms within the clusters interact strongly with framework oxygen atoms, forming partial covalent bonds, while weaker interactions occur with cavity water molecules residing in the zeolite cavities.^{32,34} These interactions facilitate electron-transfer processes that underpin the characteristic luminescence behavior of the clusters. The nature of charge-compensating cations further modulates these effects: smaller cations (Li⁺ and K⁺) impose steric hindrance, limiting water coordination and leading to blue-shifted emission, whereas larger cations (Na⁺) allow greater hydration and red-shifted or quenched emission.³⁴

Collectively, these findings reveal that the optoelectrochemical response of silver clusters in zeolites is dynamically tunable through hydration control and cation selection. Such structural and environmental sensitivity makes these materials ideal candidates for responsive optical sensing platforms, where variations in moisture, ionic composition, or molecular adsorption can be transduced into measurable luminescence signals.

Beyond water interactions, emission can be tuned across the visible spectrum by introducing ions or electron-rich molecules into zeolite pores or surfaces, which modulate the cluster's electronic environment.^{1,35,37,38} The zeolite framework structure also plays a central role in modulating the photoluminescence quantum yield (PLQY). For instance, silver clusters within Faujasite (FAU) zeolites have achieved the highest reported PLQY (97.4%), while silver clusters into Linde Type A (LTA) zeolites exhibit a low PLQY; substituting Na⁺ with Li⁺ in LTA dramatically increases the PLQY to 83%, accompanied by a redshift from blue to green/yellow emission, in addition to minimized photoblinking and photobleaching in the presence of Li⁺ cations.^{32,34,39–41} Table 1 shows the design levers for silver–cluster zeolite composites in sensing.

Another important property of silver clusters confined within zeolite frameworks is their remarkable charge transfer

Table 1 Design levers for silver-cluster zeolites

Design lever	Contribution	Photophysical response	Sensing implication	Ref.
Framework type	Controls cavity size, topology, and Ag cluster site distribution	FAU → high EQE, nanosecond decay LTA → low EQE, hundreds of micro and nano second decays	FAU → high-brightness sensors LTA → high environmental and sensitivity	42 and 43
Si/Al ratio	Modulates the framework charge and number of Ag ⁺ sites	Lower Si/Al → red shift + quenching Higher Si/Al → stronger emission	Low Si/Al → high sensitivity but lower stability High Si/Al → stable sensing	42
Extra-framework cations (Li ⁺ , Na ⁺ , and K ⁺)	Alters the local electric field, polarizability, and cluster stabilization	Small cations (Li ⁺ and K ⁺) → blue shift Larger cations (Na ⁺) → red shift + quenching Li ⁺ in LTA increases external quantum efficiencies.	Cation engineering for brightness Wavelength tuning	39 and 43
Hydration state	H ₂ O modifies cluster coordination and electronic coupling.	Fully hydrated → yellow emission Partially hydrated (2–17% water content) → blue/green emission 1% water content → blue emission	Wavelength tuning Humidity sensing	31 and 39
Surface chemistry/functionalization	Modification of the electronic environment Specificity to target analytes	Amines: Ag–N → blue shift Biomolecules → red shift	Sensing by changes in the emission	1 and 16

External quantum efficiencies (EQEs).



capability, enabling efficient electron exchange between the confined clusters and surrounding redox species such as analytes or mediators in electrochemical systems.⁴⁴ For instance, silver clusters embedded in FAU zeolite have been shown to exhibit enhanced electron-exchange-transfer and improved conductivity due to strong Ag-framework interactions and partial charge delocalization.³¹ The porous structure of the zeolite further facilitates analyte adsorption and local preconcentration, thereby increasing the electroactive surface area and improving electrode-analyte interactions.⁷

These synergistic effects, combining the redox activity of silver clusters (Ag^+/Ag^0) cycling with the ion-exchange and confinement properties of zeolites, lead to measurable improvements in the charge transfer resistance, catalytic current, and sensitivity in electrochemical assays.⁷ Consequently, silver cluster-zeolite composites act as efficient electron mediators and electrocatalytic platforms, bridging molecular-like redox behavior with robust solid-state conductivity, essential for next-generation (bio)sensing technologies.

Expanding (bio)sensing applications of silver cluster-zeolite composites

Chemical sensing: from gas detection to hybrid optical-electrochemical platforms. Despite their promising opto-electrochemical properties, few sensors that fully exploit the ability of silver clusters to interact with their electronic environment have been developed. Early studies in the 1960s reported colorimetric responses of silver-zeolite composites to water content.⁴⁵ Subsequent research attributed these effects to the formation of silver clusters within zeolite cavities, which respond actively to water molecules, paving the way for sensors targeting gases and volatile compounds.⁴⁶ For example, formaldehyde detection has been achieved *via* both colorimetric and fluorometric modes, based on the oxidation of silver clusters in intermediate valence states (Ag^0/Ag^+).^{47,48} Initially, silver clusters dissociate molecular oxygen, which reacts with formaldehyde, altering the valence state from Ag^0 to Ag_2O and Ag^+ to Ag^0 . This electron transfer, involving oxygen and the zeolite framework, leads to a visible color change (white to black) and reduced emission intensity due to cluster degradation and nanoparticle formation. This effect is more observable in zeolites with Na^+ as the counterbalancing cation, whereas Li^+ -based frameworks offer greater luminescence stability.⁴⁸

A reversible hydration-dehydration sensor was later developed using the LTA zeolite, demonstrating on-off luminescence switching. In the hydrated state, silver clusters exist as $\text{Ag}_4(\text{H}_2\text{O})_4^{2+}$, coordinated with water molecules. Upon thermal treatment, dehydration drives the conversion of $\text{Ag}_4(\text{H}_2\text{O})_4^{2+}$ into larger $\text{Ag}_6(\text{O}_4\text{R})_{14}^{2+}$ clusters, where silver atoms establish coordination with the framework oxygen atoms (O_4R groups) instead of water ligands. This structural rearrangement alters the local electronic environment and governs the observed emission shift. This reversible transformation, governed by the equation: $\text{Ag}_4(\text{H}_2\text{O})_4^{2+} + 2\text{Ag}^+ \leftrightarrow \text{Ag}_6(\text{O}_4\text{R})_{14}^{2+} + 2\text{X}^+$, modulates the emission wavelength and intensity through changes in Ag-O bonding and electron-transfer dynamics.^{34,39,49} Such

reversible switching at the atomic level, non-commonly observed in other luminescent nanomaterials, exemplifies how zeolite-embedded clusters are redefining stability and reusability in chemical sensing.

Building on the luminescence responsiveness of silver clusters, strong coordination bonds such as Ag-N can outcompete Ag-O interactions with the zeolite framework or water molecules, thereby locally redistributing electron density and triggering measurable emission changes.¹⁶ A reversible amine gas sensor was developed using silver cluster-zeolite composites. Exposure to triethylamine gas quenched luminescence and induced a blue shift (530 nm to 480 nm), attributed to the formation of Ag-N coordination bonds that disrupt Ag-O interactions. Subsequent exposure to acetic acid vapor restored the original emission by reversing the coordination and reestablishing Ag-O bonds.⁵⁰

A dual-mode oxygen sensor was also demonstrated using silver clusters in FAU zeolites. Initially orange-emitting clusters, generated under a H_2 atmosphere, transitioned to a weak cyan-emitting state upon exposure to O_2 gas. This change, driven by triplet-triplet interactions and slow diffusion of oxygen into zeolite channels, altered the electron density of the luminescent center and shortened the emission lifetime. The original state was restored under vacuum and H_2 conditions.⁵¹ This is a relevant example of how zeolite confinement provides reversible and multi-signal response in sensing.

Beyond luminescence, silver clusters in zeolites have enabled hybrid optical-electrochemical sensing platforms. Their small band gap facilitates hole injection and efficient electron-hole recombination, functioning as charge traps or donor centers.⁴⁴ While zeolites are inherently non-conductive, their porous structure enhances electrochemical performance by retaining the analytes and promoting electron transfer in the presence of silver clusters.¹⁸ An electrocatalytic sensor for hydrogen peroxide (H_2O_2) was developed using silver nanocomposites in NaY zeolite, incorporated into a carbon paste electrode. Amperometric measurements in phosphate buffer solution (PBS) revealed enhanced current response due to improved charge transfer and diffusion control.⁵² A more complex two-step system was later designed for tryptophan (Trp) detection. Silver clusters first undergo electrochemical oxidation ($\text{Ag} \rightarrow \text{Ag}^+$), followed by complexation with Trp to form $\text{Ag}(\text{Trp})_2^{3-}$, facilitating electron transfer during Trp oxidation. Compared to conventional electrodes, this system offered improved sensitivity and cost-efficiency, attributed to the nanometric size of silver clusters and zeolite mesoporosity.⁵³

A sophisticated dual-mode sensor for sulfadiazine detection has also been reported. Optical enhancement occurred *via* charge transfer, as absorption of the sulfadiazine band aligned with the silver cluster band gap in franzinite zeolites. The molecule altered the HOMO-LUMO configuration of the clusters, reducing the band gap and increasing fluorescence. The electrochemical performance was also improved, with silver clusters increasing the active sites and reducing the resistance. Compared to unmodified electrodes, this setup achieved a 2.6-fold increase in the electroactive surface area and an



Highlight

approximately 2-fold increase in the charge transfer rate, enabling ultra-trace detection across two linear ranges.⁵⁴

Altogether, these examples illustrate how embedding silver clusters within zeolite frameworks transforms chemical sensing. Silver cluster-zeolite composites uniquely couple molecular-like optical transitions with the robustness and porosity of crystalline frameworks. This synergy enables reversible switching, dual-mode readouts (optical-electrochemical), and ultra-trace detection, features rarely attainable in traditional sensor platforms. Zeolites provide a high level of control over sensor performance by tuning the emission through host-guest chemistry, and enhancing electrochemical charge transfer, demonstrating that silver cluster-zeolite composites are redefining how chemical sensing can be implemented, obtaining highly tunable, multifunctional, and robust sensing platforms.

Biosensing interfaces: toward selective and wash-free detection. Despite their biocompatibility, chemical stability, strong optical and electrochemical responses, and capacity to capture and immobilize analytes, silver cluster-zeolite composites remain underexplored in biosensing applications. A key limitation lies in the non-specific nature of the zeolite surface, which hinders its function as a biorecognition element. This challenge has been addressed through the development of an immunosensing platform that incorporates antibodies onto the surface of FAU-type zeolites embedding silver clusters. Such approaches demonstrate the high versatility of these platforms, including functionalization with appropriate biomolecules (e.g., antibodies), and enabling the detection of a wide range of analytes, including proteins and bacteria.¹

Detection is based on the sensitivity of silver clusters to local surrounding media. Upon formation of an antibody-analyte immunocomplex on the zeolite surface, the luminescence intensity of the silver clusters is modulated. The proposed mechanism involves an antenna-like donor-acceptor effect analogous to the system reported for chromophores confined within zeolite channels,^{55,56} in which guest molecules act as light-harvesting donors that transfer excitation energy to terminal “stopcock” acceptors at the crystal surface through short-range dipole-dipole coupling. Efficient interaction in such architectures requires nanometric donor-acceptor separations (typically within 2–6 nm) and appropriate spectral overlap.

In the present silver cluster-zeolite immunosystem, the silver clusters serve as luminescent donors and the immunocomplex acts as a non-luminescent acceptor that modulates the donor's emission upon analyte binding. Analyte recognition alters the electronic environment of the acceptor, facilitating energy transfer and triggering a measurable luminescence change. This mechanism supports a rapid (5 to 20 min), wash-free detection strategy with demonstrated potential in complex matrices such as human serum.¹

Altogether, these advances highlight how embedding silver clusters within zeolites might result in the enhancement of biosensors; in fact, while conventional biosensing platforms, often require washing, labelling, and/or multiple signal amplification steps, on the other hand silver cluster-zeolite composites inherently combine strong luminescence, redox activity,

and facile surface functionalization. This synergy enables fast, selective, and wash-free detection in complex media, paving the way for portable and minimally invasive diagnostic devices and redefining the path toward next-generation healthcare diagnostics. Fig. 1 summarizes different mechanisms for (bio)chemical sensors using zeolites embedding silver clusters.

Toward portable sensing: integrating silver cluster-zeolite composites into optical and electrochemical devices. A prototype humidity sensor was developed by modifying a quartz plate with a polymeric aqueous suspension containing silver clusters embedded in zeolites as the luminescent active material. This design leveraged the high sensitivity of silver clusters to water content within zeolite cavities. The sensor exhibited a distinct emission shift from yellow-green to blue, with the photoluminescence quantum yield decreasing from 62% (hydrated) to 21% (dehydrated). Although evaluated only as a proof of concept, this prototype demonstrated the feasibility of using silver cluster-zeolite composites in portable optical sensors.⁴⁹

More recently, the first portable and disposable electrochemical device incorporating silver clusters in zeolite composites was introduced. In this system, the working electrode surface of electrochemical strips was modified with zeolites embedding silver clusters, enhancing analyte immobilization, electrode-analyte interaction, and electron transfer. Two detection mechanisms were evaluated through the (i) redox reactivity where the oxidative-reductive potential of silver clusters was demonstrated through chloride ion detection. In the presence of Cl^- , Ag^0 is oxidized to Ag^+ , forming AgCl , a key reaction in environmental and biomedical analysis; and (ii) electrocatalysis, in this approach the proof of concept was tested on two substrates, filter paper and polyester. Fig. 2, illustrates the advances in the development of portable biosensor devices using silver clusters embedded within zeolites.

Filter paper strips offered lower detection limits due to higher porosity, while polyester strips provided greater sensitivity through more uniform electrode printing. The electrocatalytic activity was further evaluated for glucose detection using glucose oxidase. The electrochemical reduction of H_2O_2 , generated by the enzymatic reaction, showed enhanced sensitivity and lower detection limits compared to unmodified strips, attributed to improved electron transfer and analyte interaction. This work establishes a foundation for developing portable (bio)sensors by integrating silver cluster-zeolite composites, improving both portability and response time.⁷ However, despite these advancements, practical applications still face significant limitations in terms of stability and property control following integration into miniaturized platforms. The following section discusses the key challenges and future directions that must be addressed to enable a successful transition from early prototypes to robust, portable (bio)sensing technologies.

From prototypes to practical devices: challenges, outlook and future directions

The transition of silver cluster-zeolite composites from laboratory prototypes to practical portable devices requires overcoming



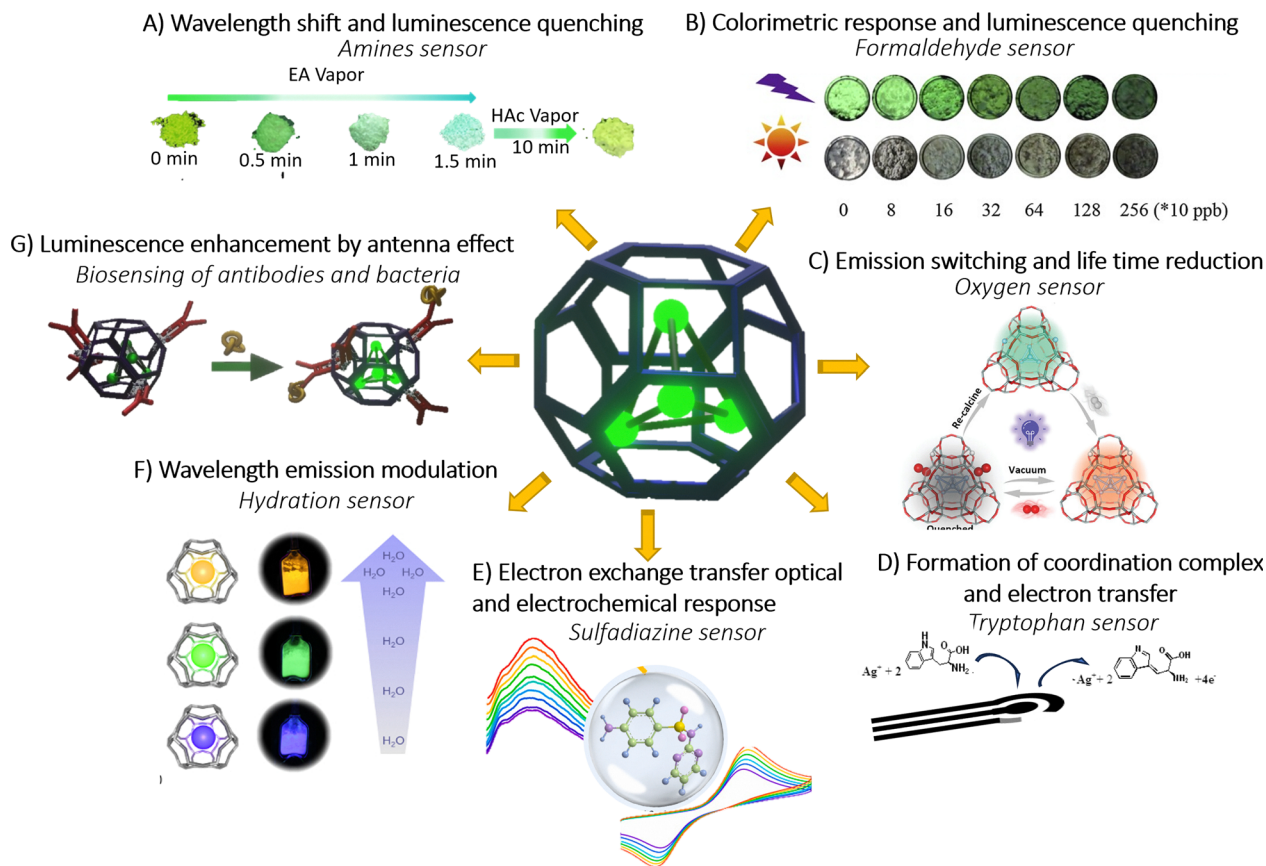


Fig. 1 Different mechanisms for (bio)chemical sensors using zeolites embedding silver clusters. (A) Wavelength shift and luminescence quenching. Adapted with permission from ref. 50 Copyright 2023, American Chemical Society. (B) Colorimetric response and luminescence quenching. Adapted with permission from ref. 47 Copyright 2020, Elsevier. (C) Emission switching and life-time reduction. Adapted with permission from ref. 51 Copyright 2024, American Chemical Society. (D) Formation of the coordination complex and electron transfer. Adapted with permission from ref. 53 Copyright 2024, Springer Nature. (E) Electron-exchange-transfer (optical and electrochemical responses). Adapted with permission from ref. 54 Copyright 2024, Elsevier. (F) Wavelength emission modulation. Adapted from ref. 49 Copyright 2016, The authors, published by JoVE licensed under the license indicated (G) Luminescence enhancement by the antenna effect. Adapted from ref. 1 Copyright 2023, The authors, published by *Angewandte* licensed under the license indicated.

challenges that range from specific material-level limitation to broad technological barriers. Addressing these systematically will be key to transforming silver cluster-zeolite composites from proof-of-concept into robust platforms for portable (bio)sensing. For instance, achieving precise control of their optoelectrochemical properties and their successful integration into stable and miniaturized devices remain a critical challenge that must be addressed.

At the structural level, zeolite architecture and surface chemistry strongly influence analyte-cluster interactions. Tailoring pore sizes (micro, meso, or hybrid structures) and morphologies, such as nanozeolites, could increase sensitivity and selectivity by enhancing analyte selectivity access to active sites.

At the material-specific level, control over their optoelectrochemical properties, including quantum yields, excitation-emission wavelengths, and charge transfer efficiency, remains a major challenge, directly affecting biosensor sensitivity and detection limits. The commonly used ion-exchange method produces silver clusters with variable sizes. Achieving atomically precise cluster nucleation and growth under well-defined

conditions could improve sensitivity and reproducibility. In parallel, strategies to tune excitation-emission wavelengths would have a significant impact on various applications. Currently, excitation typically occurs around 300 nm (250–320 nm), a range where common substrates like glass, polyester and polystyrene exhibit high absorption, limiting excitation efficiency. Importantly, photodamage (when exposure to prolonged irradiation on these wavelengths) leading local heating, photo-oxidation of the zeolite framework, or degradation of nearby biomolecules should also be experimentally considered. Moreover, for biomedical applications, red/infrared emission is essential to minimize absorption by biological tissues. Potential approaches include bimetallic cluster formation (*i.e.* with gold) or the incorporation of functional molecules into zeolite cavities near the clusters.¹⁶ Both strategies remain largely unexplored and require further theoretical and experimental investigation to understand how molecular environments modulate the photophysics of metallic clusters. In addition, biofouling of zeolite surfaces or Ag⁺ leaching or cytotoxicity could be an issue in biomedical applications;



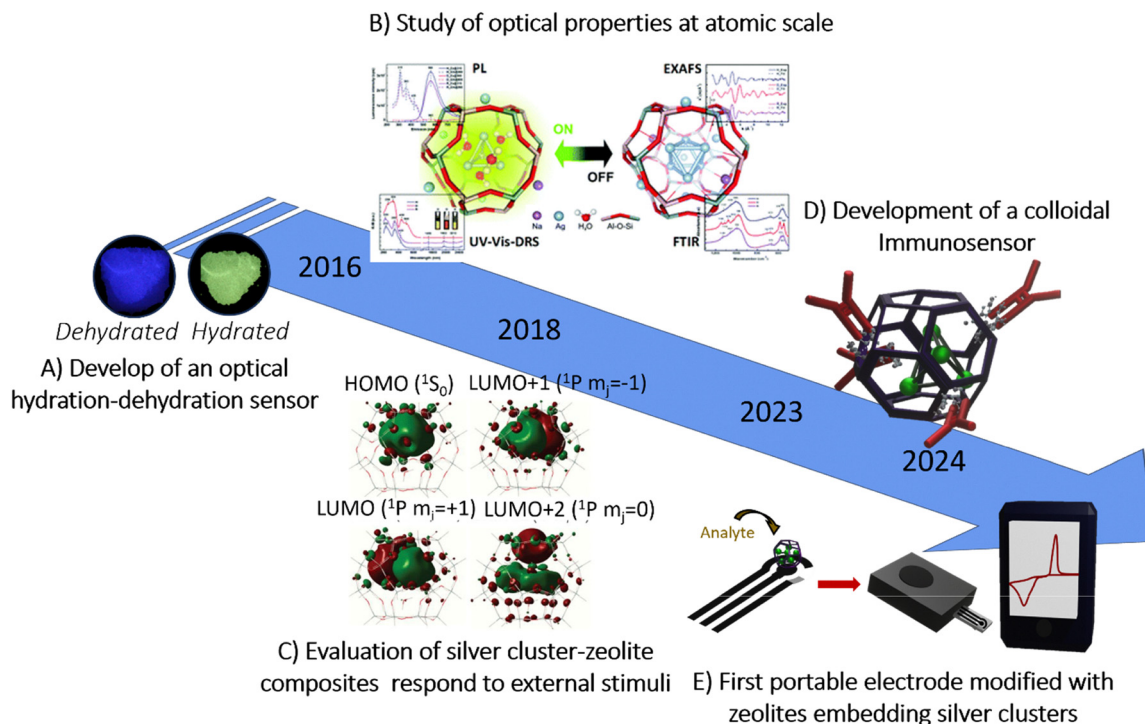


Fig. 2 Advances in the development of portable biosensor devices using silver clusters embedded into zeolites. (A) Development of an optical hydration–dehydration sensor. Adapted from ref. 49 Copyright 2016, The authors, published by *Journal of Visualized Experiments (JoVE)* licensed under the license indicated. (B) Study of optical properties at the atomic scale. Adapted with permission from ref. 34 Copyright 2018, Royal Society of Chemistry. (C) Evaluation of silver cluster–zeolite composites response to external stimuli. Adapted with permission from ref. 31 Copyright 2018, Science. (D) Development of a colloidal immunosensor. Adapted from ref. 1 Copyright 2023, The authors, published by *Angewandte* under the license indicated. (E) First portable electrode modified with zeolites embedding silver clusters. Adapted with permission from ref. 7 Copyright 2024, The authors, published by *American Chemical Society* under the license indicated.

however, surface passivation, antifouling coatings, red-shift strategies, and on-chip optical filtering could be considered to address the aforementioned challenges.

Surface functionalization is crucial for specificity. While antibodies have been demonstrated as effective biorecognition elements,¹ a broader exploration of biomolecules, such as aptamers, enzymes, or engineered proteins, as well as diverse attachment strategies could expand the scope of detectable analytes and improve device versatility. When integrating these biomolecules, it is important to consider their limited accessibility to the microporous interior of zeolites and the potential steric hindrance that may arise at the external surface, as these factors can influence the efficiency of analyte recognition and the kinetics of the sensing response. The use of nanozeolite particles can help mitigate these constraints by increasing the external surface area and improving the accessibility and orientation of immobilized biomolecules, thereby broadening the range of viable biorecognition architectures for silver-cluster-based sensing interfaces. At the same time, the underlying detection mechanisms are not yet fully understood, and further research is needed to elucidate these mechanisms across different classes of analytes.

At the broadest level, stability and reproducibility remain pressing issues. Although silver cluster–zeolite composites demonstrate intrinsic stability, systematic studies evaluating

their performance after biomolecular functionalization and incorporation into sensing platforms are still lacking. Such studies are essential to assess device longevity and operational robustness under real-world conditions. For commercial deployment, scalable, reproducible, and cost-effective synthesis methods are also critical. While zeolite synthesis has already been scaled successfully, equivalent efforts for silver cluster–zeolite composites, particularly those functionalized for biosensing, remain underdeveloped.

Device-level integration represents some of the major challenges. Embedding silver cluster–zeolite composites into microfluidic or lateral-flow systems could enable rapid and low-cost point-of-care testing. The use of biodegradable polymers as substrates would support sustainable fabrication by reducing the environmental burden and manufacturing costs. However, integration must be achieved without compromising the intrinsic luminescence and/or electrochemical properties, ensuring stable bonding with the device, maintaining effective analyte interaction. Substrate compatibility is also essential, as many device materials may interfere with efficient excitation–emission collection, making it necessary to select UV-transparent substrates (*e.g.*, quartz) or incorporate suitable waveguides/filters to ensure proper optical delivery and read-out.

Finally, incorporating advanced data analysis, particularly through machine learning algorithms, could significantly



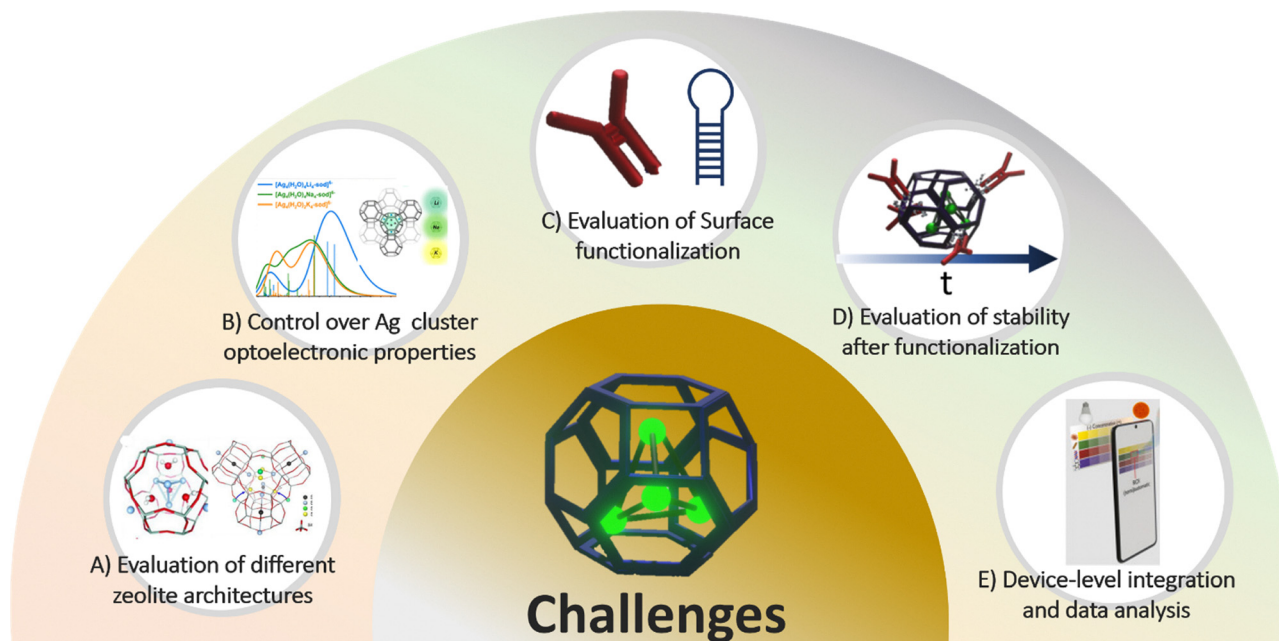


Fig. 3 Challenges of the integration of silver cluster–zeolite composites into a portable device. (A) Evaluation of different zeolite architectures. Adapted with permission from ref. 28 Copyright 2016, *American Chemical Society* and ref. 31 Copyright 2018, *Science*. (B) Control over Ag cluster optoelectronic properties. Adapted with permission from ref. 59 Copyright 2024, *American Chemical Society*. (C) Evaluation of surface functionalization. (D) Evaluation of the stability and reproducibility after functionalization. Adapted from ref. 1 Copyright 2023, the authors, published by *Angewandte* under the license indicated. (E) Device-level integration and data analysis incorporation. Adapted with permission from ref. 57 Copyright 2025, Elsevier.

enhance the interpretation of complex optical and electrochemical signals, improve sensitivity and enable real-time diagnostics.^{57,58} Fig. 3 summarized the challenges of the integration of silver cluster–zeolite composites into a portable device.

By addressing these challenges and opportunities, silver cluster–zeolite composites could evolve from proof-of-concept demonstrations into scalable, robust, and sustainable sensing platforms. This would unlock their full potential for healthcare diagnostics and environmental monitoring, combining sensitivity, selectivity, and sustainability in a compact format. We believe that future research will rely on strategies that advance both material performance and device integration.

Author contributions

C. G. G., S. C., E. C.-G. and E. M.-N wrote, reviewed and edited the original manuscript.

Conflicts of interest

There are no conflicts to declare.

Data availability

The authors confirm that the data supporting the highlights of this overview are available within the article.

Acknowledgements

C. G.-G. thanks SECIHTI for the PhD fellowship. E. C.-G. gratefully acknowledges the financial support from the FWO through the research stay grant V502522N. E. M.-N. acknowledges support from the Dirección General de Asuntos del Personal Académico de la Universidad Nacional Autónoma de México (grant PAPIIT-IT100124). E. M.-N. also acknowledges support from the Fundación Marcos Moshinsky UNAM (Cátedra Moshinsky 2024) and SECIHTI (grant MADTEC-2025-M-137). E. M.-N. and S. C. acknowledge financial support from MAECI-AMEXCID (Joint Research Proposals for the Years 2023–2025, DPC01225-7/2024).

References

- 1 C. García-Guzmán, E. Morales-Narváez and E. Coutino-Gonzalez, *Angew. Chem., Int. Ed.*, 2023, e202307718.
- 2 M. Retout, L. Amer, W. Yim, M. N. Creyer, B. Lam, D. F. Trujillo, J. Potempa, A. J. O'Donoghue, C. Chen and J. V. Jokerst, *ACS Nano*, 2023, 17, 17308–17319.
- 3 J. Sakai, S. Biswas, T. Irie, H. Mabuchi, T. Sekine, Y. Niihori, S. Das and Y. Negishi, *Nanoscale*, 2023, 15, 12227–12234.
- 4 V. Nasirian, M. Shamsipur, F. Molaabasi, K. Mansouri, M. Sarparast, V. Salim, A. Barati and S. Kashanian, *Sens. Actuators, B*, 2020, 308, 127673.
- 5 Y. Chen and R. G. Compton, *Chemosensors*, 2023, 11, 297.
- 6 D. Ungor, R. Béteki, K. Horváth, O. Dömötör and E. Csapó, *Int. J. Mol. Sci.*, 2022, 23.
- 7 C. García-Guzmán, A. Raucci, E. Coutino-Gonzalez, E. Morales-Narváez and S. Cinti, *Anal. Chem.*, 2024, 96, 17915–17921.
- 8 D. Prakashan, N. S. Shrikrishna, M. Byakodi, K. Nagamani and S. Gandhi, *J. Med. Virol.*, 2023, 95, e28416.



Highlight

- 9 F. Gao, C. Liu, Y. Yao, C. Lei, S. Li, L. Yuan, H. Song, Y. Yang, J. Wan and C. Yu, *Biosens. Bioelectron.*, 2022, **199**, 113892.
- 10 E. Coutiño-Gonzalez, W. Baekelant, J. A. Steele, C. W. Kim, M. B. J. Roefsaers and J. Hofkens, *Acc. Chem. Res.*, 2017, **50**, 2353–2361.
- 11 H. Nasrollahpour, B. J. Sánchez, M. Sillanpää and R. Moradi, *ACS Appl. Nano Mater.*, 2023, **6**, 12609–12672.
- 12 E. Coutino-Gonzalez, M. Roefsaers and J. Hofkens, in *Dye. Photoactive Mol. Microporous Syst.*, 2020, pp. 75–103.
- 13 I. Díez and R. H. A. Ras, Few-Atom Silver Clusters as Fluorescent Reporters, *Advanced Fluorescence Reporters in Chemistry and Biology II: Molecular Constructions, Polymers and Nanoparticles*, Springer Berlin Heidelberg, Berlin, Heidelberg, 2010, pp. 307–332.
- 14 Y. Chai, W. Shang, W. Li, G. Wu, W. Dai, N. Guan and L. Li, *Adv. Sci.*, 2019, **6**, 1900299.
- 15 J. Yuan, Q. Li, C. Yue, N. Wang, P. Li and H. Li, *J. Mater. Chem. C*, 2023, **11**, 17080–17086.
- 16 B. Chan, *Phys. Chem. Chem. Phys.*, 2021, **23**, 1984–1993.
- 17 F. Baletto, *J. Phys.: Condens. Matter*, 2019, **31**, 113001.
- 18 H. Hirai, S. Ito, S. Takano, K. Koyasu and T. Tsukuda, *Chem. Sci.*, 2020, **11**, 12233–12248.
- 19 H. Berry, 2023. Preprint (Version 1) available at Research Square [<https://doi.org/10.21203/rs.3.rs-3716517/v1>].
- 20 T. Nishimura, T. Toba, G. Sakane and T. Ishii, *Crystals*, 2022, **12**.
- 21 X. Kang, H. Chong and M. Zhu, *Nanoscale*, 2018, **10**, 10758–10834.
- 22 X. Wu and Y. Sun, *J. Nanopart. Res.*, 2017, **19**, 201.
- 23 T. M. Soini and N. Rösch, *Phys. Chem. Chem. Phys.*, 2015, **17**, 28463–28483.
- 24 B. Jha and D. N. Singh, Basics of Zeolites, in *Fly Ash Zeolites: Innovations, Applications, and Directions*, ed. B. Jha and D. N. Singh, Springer Singapore, Singapore, 2016, pp. 5–31.
- 25 A. Walcarius, *Electroanalysis*, 1996, **8**, 971–986.
- 26 X. Zeng, X. Hu, H. Song, G. Xia, Z.-Y. Shen, R. Yu and M. Moskovits, *Microporous Mesoporous Mater.*, 2021, **323**, 111262.
- 27 X. Xv, S. Ye, L. Pan, P. Lin, H. Liao and D. Wang, *Materials*, 2022, **15**, 7431.
- 28 T. Altantzis, E. Coutino-Gonzalez, W. Baekelant, G. T. Martinez, A. M. Abakumov, G. Van Tendeloo, M. B. J. Roefsaers, S. Bals and J. Hofkens, *ACS Nano*, 2016, **10**, 7604–7611.
- 29 M. El-Roz, I. Telegeiev, N. E. Mordvinova, O. I. Lebedev, N. Barrier, A. Behilil, M. Zaarour, L. Lakiss and V. Valtchev, *ACS Appl. Mater. Interfaces*, 2018, **10**, 28702–28708.
- 30 O. Fenwick, E. Coutiño-Gonzalez, F. Richard, S. Bonacchi, W. Baekelant, D. de Vos, M. B. J. Roefsaers, J. Hofkens and P. Samorì, *Small*, 2020, **16**, 2002063.
- 31 D. Grandjean, E. Coutiño-Gonzalez, N. T. Cuong, E. Fron, W. Baekelant, S. Aghakhani, P. Schlexer, F. D'Acapito, D. Banerjee, M. B. J. Roefsaers, M. T. Nguyen, J. Hofkens and P. Lievens, *Science*, 2018, **361**, 686–690.
- 32 E. Fron, S. Aghakhani, W. Baekelant, D. Grandjean, E. Coutino-Gonzalez, M. Van der Auweraer, M. B. J. Roefsaers, P. Lievens and J. Hofkens, *J. Phys. Chem. C*, 2019, **123**, 10630–10638.
- 33 I. Chakraborty and T. Pradeep, *Chem. Rev.*, 2017, **117**, 8208–8271.
- 34 S. Aghakhani, D. Grandjean, W. Baekelant, E. Coutiño-Gonzalez, E. Fron, K. Kvashnina, M. B. J. Roefsaers, J. Hofkens, B. F. Sels and P. Lievens, *Nanoscale*, 2018, **10**, 11467–11476.
- 35 G. Romolini, J. A. Steele, J. Hofkens, M. B. J. Roefsaers and E. Coutino-Gonzalez, *Adv. Opt. Mater.*, 2021, **9**, 2100526.
- 36 E. Johan, Y. Kanda, N. Matsue, Y. Itagaki and H. Aono, *J. Lumin.*, 2019, **213**, 482–488.
- 37 J. Yu, S. Ye, H. Liao, X. Xv and D. Wang, *ACS Appl. Nano Mater.*, 2021, **4**, 13692–13699.
- 38 W. Baekelant, S. Aghakhani, E. Coutino-Gonzalez, K. Kennes, F. D'Acapito, D. Grandjean, M. Van der Auweraer, P. Lievens, M. B. J. Roefsaers, J. Hofkens and J. A. Steele, *J. Phys. Chem. Lett.*, 2018, **9**, 5344–5350.
- 39 E. Coutino-Gonzalez, W. Baekelant, D. Grandjean, M. B. J. Roefsaers, E. Fron, M. S. Aghakhani, N. Bovet, M. Van der Auweraer, P. Lievens, T. Vosch, B. Sels and J. Hofkens, *J. Mater. Chem. C*, 2015, **3**, 1627–1631.
- 40 G. De Cremer, E. Coutiño-Gonzalez, M. B. J. Roefsaers, D. E. De Vos, J. Hofkens, T. Vosch and B. F. Sels, *Chem. Phys. Chem.*, 2010, **11**, 1627–1631.
- 41 W. Baekelant, S. Aghakhani, E. Fron, C. Martin, C. Woong-Kim, J. A. Steele, T. De Baerdemaeker, F. d'Acapito, D. Chernysov, M. van der Auweraer, P. Lievens, D. Grandjean, M. Roefsaers, J. Hofkens and E. Coutino-Gonzalez, *J. Mater. Chem. C*, 2019, **7**, 14366–14374.
- 42 E. Coutino-Gonzalez, M. B. J. Roefsaers, B. Dieu, G. De Cremer, S. Leyre, P. Hanselaer, W. Fyen, B. Sels and J. Hofkens, *J. Phys. Chem. C*, 2013, **117**, 6998–7004.
- 43 G. De Cremer, E. Coutiño-Gonzalez, M. B. J. Roefsaers, B. Moens, J. Ollevier, M. Van der Auweraer, R. Schoonheydt, P. A. Jacobs, F. C. De Schryver, J. Hofkens, D. E. De Vos, B. F. Sels and T. Vosch, *J. Am. Chem. Soc.*, 2009, **131**, 3049–3056.
- 44 K. Kennes, E. Coutino-Gonzalez, C. Martin, W. Baekelant, M. B. J. Roefsaers and M. Van der Auweraer, *Adv. Funct. Mater.*, 2017, **27**, 1606411.
- 45 M. Rálek, P. Jirů, O. Grubner and H. Beyer, *Collect. Czech. Chem. Commun.*, 1962, **27**, 142–146.
- 46 D. Brühwiler, R. Seifert and G. Calzaferri, *J. Phys. Chem. B*, 1999, **103**, 6397–6399.
- 47 D. Yao, Y. Wang and H. Li, *Sens. Actuators, B*, 2020, **305**, 127451.
- 48 J. Yu, S. Ye, X. Xv, L. Pan, P. Lin, H. Liao and D. Wang, *Nanomaterials*, 2022, **12**, 3215.
- 49 E. Coutino-Gonzalez, W. Baekelant, B. Dieu, M. B. J. Roefsaers and J. Hofkens, *JoVE*, 2016, e54674.
- 50 Q. Li, X. Tian, J. Yuan, D. Zhao, Y. Wang and H. Li, *Inorg. Chem.*, 2023, **62**, 2430–2439.
- 51 L. Sun, G. Romolini, B. Dieu, D. Grandjean, M. Keshavarz, E. Fron, F. D'Acapito, M. B. J. Roefsaers, M. Van der Auweraer and J. Hofkens, *Adv. Opt. Mater.*, 2024, 2400784.
- 52 H. Ramezani, S. N. Azizi and S. R. Hosseini, *Sens. Actuators, B*, 2017, **248**, 571–579.
- 53 S.-F. Mousavi, M. Alimoradi, A. Shirmardi and V. Zare-Shahabadi, *J. Porous Mater.*, 2020, **27**, 1505–1514.
- 54 X. Zhu, Z. Li, F. Fang, E. Yifeng, P. Chen, L. Li and K. Qian, *Anal. Chim. Acta*, 2023, **1276**, 341619.
- 55 G. Calzaferri, S. Huber, H. Maas and C. Minkowski, *Angew. Chem., Int. Ed.*, 2003, **42**, 3732–3758.
- 56 G. Calzaferri, *Langmuir*, 2012, **28**, 6216–6231.
- 57 A. Horta-Velázquez, G. Ramos-Ortiz and E. Morales-Narváez, *Biosens. Bioelectron.*, 2025, **273**, 117089.
- 58 D. L. Mancera-Zapata, C. Rodríguez-Nava, F. Arce and E. Morales-Narváez, *Anal. Chem.*, 2024, **96**, 13756–13761.
- 59 L. Pan, S. Ye, R. Huang, M. Wang, T. Zheng, H. Zhang and D. Wang, *Inorg. Chem.*, 2024, **63**, 24867–24875.

