




 Cite this: *Chem. Commun.*, 2026, 62, 6759

 Received 23rd January 2026,
Accepted 3rd March 2026

DOI: 10.1039/d6cc00481d

rsc.li/chemcomm

Solvation regulation and interfacial adsorption by ethanolamine-based eutectic electrolytes toward byproduct-free zinc anodes

 Mengya Wang, Haonan Zheng, Hui Zhang, Gaorong Han, Wei-Qiang Han  and Hangjun Ying *

This study designs ethanolamine-based hydrated eutectic electrolytes to stabilize Zn anodes by coregulating the solvation structure and interfacial adsorption. EA interacts with Zn²⁺ to suppress H₂O and anion (OTf⁻) coordination, and it preferentially anchors on the Zn anode. Therefore, a superior lifespan of Zn||Zn cells of over 1800 h at 2 mA cm⁻²/2 mAh cm⁻² and enhanced stability of an active carbon cathode are obtained.

Aqueous Zn anode-based energy storage devices have received broad attention for their intrinsic safety, abundant resources, low standard potential (−0.76 V vs. SHE), and high theoretical capacities (820 mAh g⁻¹, 5855 mAh L⁻¹).¹ However, dendrite growth originating from unlimited two-dimensional (2D) Zn²⁺ diffusion and water-induced parasitic reactions arising from abundant water in a free or coordinated state confine the application of Zn anodes. Featuring high tunability, superior dissolution ability, and favorable thermal/electrochemical stability, eutectic electrolytes can resolve the above-mentioned problems.² By virtue of hydrogen-bond interactions in the eutectic network, Grothuss-mediated proton transfer and the hydrogen evolution reaction (HER) can be inhibited.³ Meanwhile, the introduced organic ligands can coordinate with Zn²⁺ through Lewis acid–base interactions and generate an adsorption layer on the Zn anode, thereby tuning interfacial phenomena like the solid–electrolyte interphase (SEI) and electric double layer (EDL).

The inherent high viscosity of deep eutectic solvents (DESS) gives rise to the large overpotential of eutectic electrolytes, promoting research into hydrated eutectic electrolytes (HEEs). Generally, substituting solid ligands like urea⁴ and acetamide⁵ with liquid ones⁶ can promote the ionic dissociation of zinc salts. Meanwhile, applying zinc salts with a high dissociation ability, like Zn(OTf)₂, also contributes to higher ionic conductivity. For example, multiple alcohol molecules, like 2-propanol,⁷ ethylene glycol,⁸ and 1,3-propanediol,⁹ are incorporated into

Zn(OTf)₂-based HEEs for commendable bulk mass transfer with confined water activity. Similarly, amino alcohols with bifunctional groups of –OH and –NH₂ exhibit high polarity for interfacial adsorption and are conducive for tuning Zn²⁺ coordination structures.^{10,11}

Herein, we construct ethanolamine (EA)-based HEEs with highly dissociated Zn(OTf)₂, in which the solvation structure and interfacial chemistry are modified for a byproduct-free Zn anode. EA interacts with H₂O through hydrogen bond interactions, and it participates in the Zn²⁺ solvation shell for reduced H₂O and OTf⁻ coordination. In addition, boosted by the preferential adsorption of EA molecules, EA-based HEEs manifest an interface where Zn²⁺ is aggregated and OTf⁻ is excluded for enhanced EDL capacitance and promoted interfacial kinetics. Consequently, a clear Zn anode surface without an OTf⁻-derived interphase is obtained, which inhibits parasitic reactions. Zn||Zn cells deliver a prolonged lifespan of 1800 h at 2 mA cm⁻²/2 mAh cm⁻². When paired with an active carbon cathode, EA-based HEEs render a higher discharge capacity with capacity retention of 85% for 5000 cycles, and deliver favorable low-temperature performance at −20 °C.

Electrostatic potential (ESP) maps of H₂O and EA molecules are shown in Fig. 1a. H₂O displays a bipolar nature. EA is an amino alcohol and contains the two distinctive functional groups of –OH and –NH₂.^{12,13} As EA is miscible with water in all proportions,¹⁴ here, we mix H₂O with EA at different volume ratios and fix the content of Zn(OTf)₂ at 1 M (mol L⁻¹), denoting 1 M Zn(OTf)₂ in H₂O:EA = 3:2 as HE32 electrolyte. Upon increasing the water content, the viscosity of HEEs decreases from 38.4 mPa s for HE14 to 5.4 mPa s for HE32, and the ionic conductivity increases from 2.6 mS cm⁻² to 13.3 mS cm⁻², suggesting more complete salt dissolution in HE32 (Fig. 1b). In terms of electrolyte performance, Zn||Zn cells with HE32 deliver the longest lifespan of 1800 h at 1 mA cm⁻²/1 mAh cm⁻², combined with a comparable overpotential with Zn(OTf)₂ electrolyte (Fig. S1, SI). In the “reservoir half-cell” galvanostatic protocol, Zn||Cu cells with HE32 deliver a higher

School of Materials Science and Engineering, Zhejiang University, Hangzhou 310027, China. E-mail: yinghangjun@zju.edu.cn



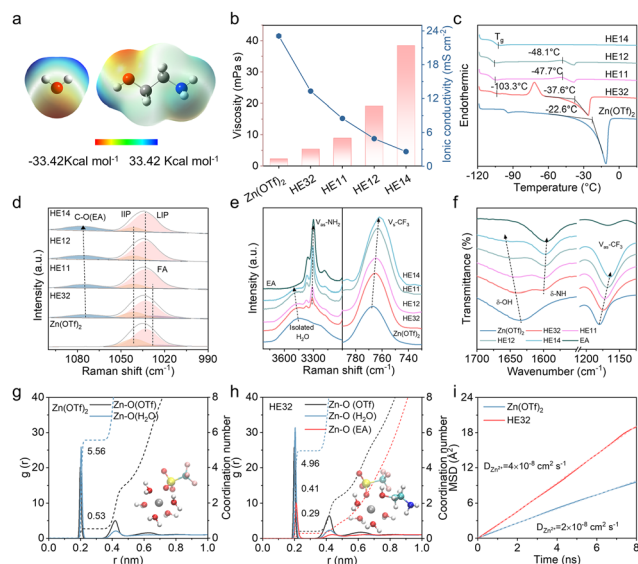


Fig. 1 The physicochemical performance and chemical coordination environment. (a) ESP maps. (b) Viscosity and ionic conductivity. (c) DSC curves. (d, e) Raman and (f) FT-IR spectra. Radial distribution functions (RDFs) and primary solvation sheaths (PSSs) of (g) Zn(OTf)₂ and (h) HE32 electrolytes. (i) MSD functions of Zn²⁺.

average CE of 98.5% with a steady voltage profile, confirming the optimal performance of HE32 electrolyte (Fig. S2, SI). Differential scanning calorimetry (DSC) shows that in the cooling process, the freezing point is greatly reduced from Zn(OTf)₂ (−27.3 °C) to HE32 electrolyte (−49.2 °C) (Fig. S3, SI). With lower water content, the melting point reduces, and the exothermic peak weakens (Fig. 1c). The consistent glass transition temperature of HEEs below −100 °C validates the formation of DESs.

Furthermore, the chemical coordination in electrolytes is analyzed *via* spectral characterization and molecular dynamics (MD) simulations (Figs S4 and S5, Table S1, SI). As shown in Fig. 1d, the symmetric stretching vibration of SO₃ can be deconvoluted into three peaks: free anions (FAs, 1028 cm^{−1}), loose ion pairs (LIPs, 1033 cm^{−1}), and intimate ion pairs (IIPs, 1041 cm^{−1}).⁸ HE14, HE12, and HE11 nearly contain no FAs, while HE32 shows more FAs and LIPs than Zn(OTf)₂, implying favored salt dissolution in HE32. With increasing EA content, the stretching vibration of C–O at 1703 cm^{−1} shifts positively, while the interaction of C–O with Zn²⁺ at 1468 cm^{−1} undergoes a red shift, suggesting the strengthened coordination of EA to Zn²⁺ (Fig. S7a, SI).¹⁵ Meanwhile, the isolated water clusters undergo a blue shift due to hydrogen bonding interactions with EA molecules, as evidenced by the redshifting of the asymmetric stretching vibration of NH₂ at 3310 cm^{−1} (Fig. 1e). The hydrogen bond number obtained from MD simulations also validates the interaction of EA and H₂O, with decreased H₂O–H₂O interactions (Fig. S6, SI). The symmetric stretching vibration of CF₃ at 766 cm^{−1} experiences a red shift, suggesting a shortened C–F bond length and stabilized OTf[−] anions in HEEs. These findings are in line with the Fourier-transform infrared (FT-IR) spectroscopy results (Fig. 1f and Fig. S7b, SI).^{16,17}

MD simulation results are presented in Fig. 1g and h. Zn(OTf)₂ electrolyte delivers a nearly fully hydrated solvation

shell with 5.56 H₂O and 0.53 OTf[−] participating. However, in HE32 electrolyte, EA, with a higher electron-donating ability than H₂O, reduces the number of solvated H₂O and OTf[−] anions, giving rise to a solvation structure of Zn(H₂O)_{4.96}(OTf)_{0.41}(EA)_{0.29}^{1.59+}. The lower hydration degree of Zn²⁺ in HE32 electrolyte decreases water activity and contributes to promoting bulk Zn²⁺ transfer. According to the mean square displacement (MSD) of Zn²⁺, HE32 electrolyte displays a higher self-diffusion coefficient of 4 × 10^{−8} cm² s^{−1} than Zn(OTf)₂ electrolyte (2 × 10^{−8} cm² s^{−1}) (Fig. 1i). The Zn²⁺ transference number in HE32 electrolyte also shows a larger value of 0.39 than in Zn(OTf)₂ electrolyte (0.11) (Fig. S8, SI), validating the promoted Zn²⁺ diffusion in EA-based HEEs.

With regard to interfacial behavior, the bifunctional groups in EA will provide multiple anchor sites on the Zn anode. EA demonstrates a higher-energy highest occupied molecular orbital (HOMO) and lower-energy lowest unoccupied molecular orbital (LUMO) than H₂O, suggesting easier electron exchange between EA and Zn metal (Fig. 2a).¹⁸ Consequently, EA molecules show a larger adsorption energy of −2.31 eV than H₂O (−0.28 eV), verifying the preferential adsorption behavior of EA on the Zn metal surface (Fig. 2b).⁴ To monitor the interfacial EDL structure, EDL capacitance in the non-faradaic region and differential capacitance (DC) obtained by impedance-potential testing are measured. The fitted EDL capacitance of Zn||Zn cells in HE32 is about 30 times higher than that in Zn(OTf)₂ electrolyte (2993 μF cm^{−2} vs. 92 μF cm^{−2}) (Fig. 2c and Fig. S9, SI). Based on the equation $C = \epsilon A/d$, the increase in C (EDL capacitance) implies an increase in A (electrode effective surface area) and a decrease in d (EDL thickness).¹⁹ The DC values obtained from Zn||Cu cells manifest an identical tendency: HE32 shows higher values in the range of 0.2–0.6 V (Fig. 2d). As

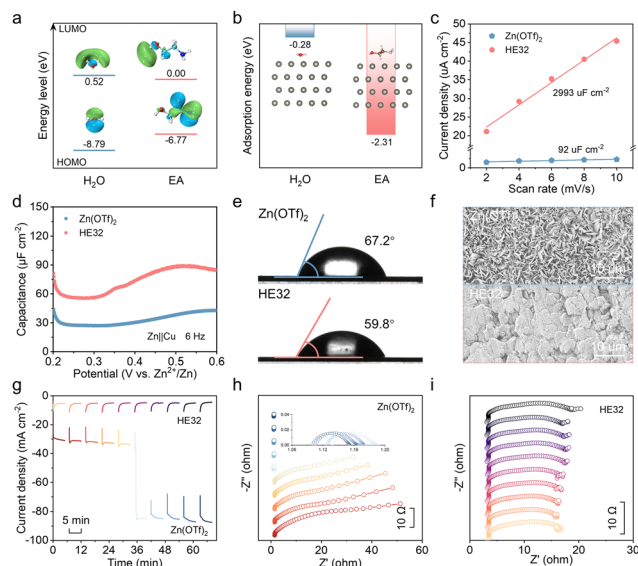


Fig. 2 Preferential adsorption behavior and interface stability. (a) HOMO/LUMO energy levels and (b) adsorption energies on the Zn (002) plane. (c) EDL capacitances of Zn||Zn cells. (d) DCs of Zn||Cu cells. (e) Contact angles. (f) SEM images of Zn anodes saturated for 48 h. Sequential (g) CA curves and EIS plots in (h) Zn(OTf)₂ and (i) HE32 electrolytes.



DC reflects the total charge of ions adsorbed on the Zn anode surface, higher DC in HE32 electrolyte suggests the exclusion of OTf⁻ at the electrode–electrolyte interface, reducing parasitic reactions, and the aggregation of Zn²⁺ for dense and homogeneous Zn²⁺ deposition.²⁰

In contact angle measurements, HE32 electrolyte shows a lower contact angle on the Zn anode than Zn(OTf)₂ electrolyte (59.8° vs. 67.2°) (Fig. 2e). The promoted wettability and hydrophilicity in HE32 electrolyte help to guide smooth Zn deposition. After saturation for 48 h, the Zn anode in HE32 electrolyte delivers a compact surface. However, in Zn(OTf)₂ electrolyte, the Zn anode is covered by massive irregular byproducts, and the effective surface area of the Zn anode is accordingly decreased (Fig. 2f).

Fig. S10, SI, reveals the chronoamperometry (CA) curves, where Zn(OTf)₂ electrolyte shows continuously increased current density and apparent Zn²⁺ 2D diffusion. Sequentially coupled CA and electrochemical impedance spectroscopy (EIS) measurements were applied to investigate the Zn²⁺ deposition behavior. CA in Zn(OTf)₂ electrolyte exhibits a larger current response in total and experiences a sharp decrease (Fig. 2g). As elucidated by EIS plots, due to unrestricted Zn²⁺ 2D diffusion to easy deposition sites, protrusions grow gradually, the interfacial impedance decreases, and short circuits occur (Fig. 2h). However, in HE32, the current density stabilizes quickly upon the start of CA testing, indicating well-regulated Zn²⁺ 3D diffusion by the EA adsorption layer. Afterwards, Zn||Zn cells exhibit nearly identical CA plots, and the EIS curves remain steady throughout the deposition process, verifying the consistent uniform deposition (Fig. 2i).

In terms of interfacial kinetics, HE32 delivers incredibly smaller charge transfer resistance (R_{ct}), and the activation energy decreases to 38.94 kJ mol⁻¹, lower than that of Zn(OTf)₂ (50.83 kJ mol⁻¹) (Fig. 3a, Fig. S11, SI). The promoted EDL capacitance and enhanced wettability in HE32 help to accelerate the interfacial dynamics. In addition, Zn(OTf)₂ electrolyte exhibits larger yet more volatile CV curves, implying rapid mass transfer and a volatile interface in aqueous electrolyte (Fig. 3b and c). The consistent CV curves in HE32 verify that a stable interface is generated at first and is sustained over repeat cycles (Fig. S12, SI).

Tafel plots reflect a much lower corrosion current density of 2.02 mA cm⁻² in HE32 electrolyte (Fig. 3d). After 50 cycles, the Zn anode in HE32 exhibits no parasitic products of the form Zn_x(OTf)_y(OH)_{2x-y}·nH₂O, and shows a higher tendency for Zn (002) growth ($I_{(002)/(100)} = 2.35$) (Fig. 3e).²¹ Conversely, Zn(OTf)₂ electrolyte manifests a higher corrosion current density of 3.07 mA cm⁻², and the cycled Zn anode shows multiple signals from byproducts.

The XPS spectrum of the cycled Zn anode in HE32 exhibits a higher content of C–O/C–N, confirming the adsorption of EA molecules (Fig. 3f). Meanwhile, the C 1s spectrum shows no signal from CF₃, and the F 1s and S 2p spectra manifest quite weak peaks, fully verifying the exclusion of H₂O and OTf⁻ from the Zn surface (Fig. 3g and h). The negatively shifted Zn 2p peak in HE32 electrolyte also implies fewer generated byproducts (Fig. S13, SI). However, in Zn(OTf)₂ electrolyte, desolvated and

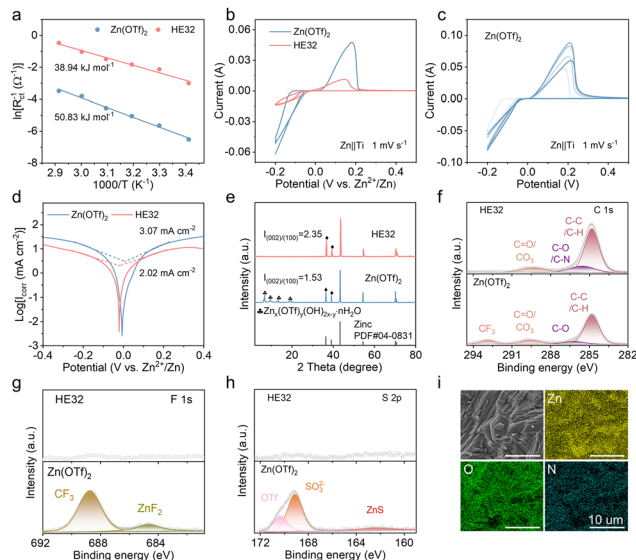


Fig. 3 Interfacial dynamics and component analysis. (a) Activation energies. (b) The first CV cycles of Zn||Ti cells at 1 mV s⁻¹ and (c) CV curves for 5 cycles in Zn(OTf)₂ electrolyte. (d) Tafel plots of Zn||Zn cells. (e) XRD patterns of cycled Zn anodes and (f) C 1s. (g) F 1s, and (h) S 2p XPS fine spectra. (i) SEM images and mapping results of a cycled Zn anode in HE32.

interfacially adsorbed OTf⁻ anions will experience reduction and generate massive mossy byproducts like Zn_x(OTf)_y(OH)_{2x-y}·nH₂O, ZnF₂, and ZnS. SEM images of the cycled Zn anode in HE32 show a compact deposition morphology (Fig. 3i). The uniform distribution of Zn, O, and N elements indicates the beneficial effect of the EA adsorption layer for even Zn²⁺ deposition. The energy spectra and element proportions given in Fig. S14, SI, also validate the absence of F and S elements on the Zn metal surface.

To confirm the practicability of HE32 electrolyte, the electrochemical performances of Zn||Zn and Zn||Cu cells, and full batteries paired with active carbon (AC), are evaluated. Due to enhanced interfacial kinetics, Zn||Zn cells in HE32 show drastically decreased R_{ct} under open-circuit conditions and after 50 cycles (Fig. 4a and Fig. S15, SI). Fig. 4b shows the cycling performance of Zn||Zn cells at 2 mA cm⁻²/2 mAh cm⁻². The cell in Zn(OTf)₂ electrolyte undergoes rapid short-circuiting. HE32 electrolyte enables the steady operation of a Zn||Zn cell for 1800 h, and the overpotential is comparable with that in aqueous solution (Fig. S16, SI). In terms of rate performance, HE32 operates normally from 0.2 mA cm⁻² to 3 mA cm⁻², and the overpotential reduces slightly (Fig. 4c). However, in Zn(OTf)₂ electrolyte, Zn||Zn cells malfunction during the second 0.5 mA cm⁻² step. The cycled Zn anode in Zn(OTf)₂ is mossy and irregular, full of loose byproducts, while the Zn anode in HE32 displays compact morphology with a (002) orientation (Fig. 4d).

Zn||Cu cells with HE32 electrolyte operate steadily at 1 mA cm⁻² for 2000 cycles and the average CE is 99.41%, higher than the chaotic distribution in Zn(OTf)₂ (Fig. 4e). The corresponding voltage profiles present better consistency in HE32 (Fig. 4f). In HE32 electrolyte, the enhanced wettability toward the AC cathode (Fig. S17, SI), the dramatically low



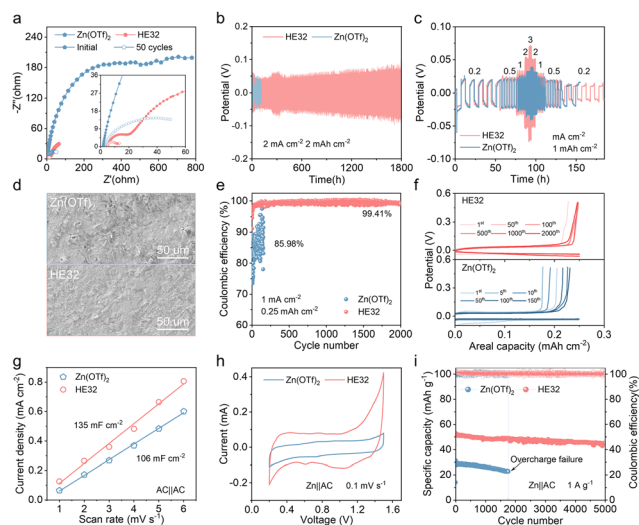


Fig. 4 The electrochemical performance of electrolytes. (a) Nyquist plots of Zn||Zn cells. (b) Cyclic performance of Zn||Zn cells. (c) Rate performance. (d) SEM images of cycled Zn anodes. (e) CEs and (f) voltage profiles of Zn||Cu cells. (g) EDL capacitance of AC||AC cells. (h) CV curves and (i) cyclic performance of Zn||AC cells.

interfacial impedance (R_{inter}) and R_{ct} values (Fig. S18, SI), and the larger EDL capacitance of the AC cathode (Fig. 4g and Fig. S19, SI) contribute to improved energy storage. Larger-area CV curves are observed in HE32 electrolyte (Fig. 4h). Therefore, HE32 electrolyte delivers an initial discharge capacity of 53 mAh g^{-1} , and achieves capacity retention of 85% for 5000 cycles at 1 A g^{-1} (Fig. 4i and Fig. S20, SI). At different rates, HE32 electrolyte enables higher capacities (Fig. S21, SI). Assisted by the low freezing point, HE32 electrolyte remains stable at -20°C and renders steady operation at 0.1 A g^{-1} for 100 cycles (Figs. S22 and S23, SI).

In conclusion, we design EA-based HEEs with highly dissociated $\text{Zn}(\text{OTf})_2$, achieving a byproduct-free Zn anode through coregulating the solvation structure and interfacial adsorption. EA with $-\text{OH}$ and $-\text{NH}_2$ confines water in a eutectic network *via* hydrogen bond interactions, and reduces the content of solvated H_2O and OTf^- by Lewis acid–base interactions with Zn^{2+} . In addition, the preferential adsorption of EA on the Zn anode induces an interface where Zn^{2+} is aggregated, while H_2O and OTf^- are repelled for enhanced EDL capacitance and interfacial kinetics. Consequently, a clear Zn anode surface without apparent OTf^- reduction is achieved for inhibited side reactions. Zn||Zn cells show a superior lifespan of 1800 h at $2 \text{ mA cm}^{-2}/2 \text{ mAh cm}^{-2}$. Zn||AC full batteries deliver a capacity retention of 85% for 5000 cycles at 1 A g^{-1} , and enable steady operation at -20°C . This work provides insights into modulating Zn^{2+} coordination structures and interfacial adsorption for enhanced metal-anode interfacial stability.

Conflicts of interest

There are no conflicts to declare.

Data availability

The data supporting this article have been included as part of the supplementary information (SI). Supplementary information is available. See DOI: <https://doi.org/10.1039/d6cc00481d>.

Acknowledgements

This work was supported by the Natural Science Foundation of Zhejiang Province (no. LY23E020008), the Fundamental Research Funds for the Central Universities (no. 226-2024-00195), and the Key Research and Development Program of Zhejiang Province (no. 2023C01127).

References

- Y. F. Qu, J. W. Qian, F. Zhang, Z. Zhu, Y. Zhu, Z. Hou, Q. Meng, K. Chen, S. X. Dou and L. F. Chen, *Adv. Mater.*, 2024, 2413370.
- M. Wang, Z. Xu, C. He, L. Cai, H. Zheng, Z. Sun, H. K. Liu, H. Ying and S. Dou, *ACS Nano*, 2025, 19, 9709–9739.
- M. Li, Z. Li, X. Wang, J. Meng, X. Liu, B. Wu, C. Han and L. Mai, *Energy Environ. Sci.*, 2021, 14, 3796–3839.
- Z. Wang, J. Diao, J. N. Burrow, K. K. Reimund, N. Katyal, G. Henkelman and C. B. Mullins, *Adv. Funct. Mater.*, 2023, 33, 2304791.
- S. Wang, S. Chen, Y. Ying, G. Li, H. Wang, K. K. Cheung, Q. Meng, H. Huang, L. Ma and J. A. Zapien, *Angew. Chem., Int. Ed.*, 2024, e202316841.
- D. Wang, H. Peng, S. Zhang, H. Liu, N. Wang and J. Yang, *Angew. Chem., Int. Ed.*, 2023, e202315834.
- Q. Ma, R. Gao, Y. Liu, H. Dou, Y. Zheng, T. Or, L. Yang, Q. Li, Q. Cu, R. Feng, Z. Zhang, Y. Nie, B. Ren, D. Luo, X. Wang, A. Yu and Z. Chen, *Adv. Mater.*, 2022, 34, 2207344.
- R. Chen, C. Zhang, J. Li, Z. Du, F. Guo, W. Zhang, Y. Dai, W. Zong, X. Gao, J. Zhu, Y. Zhao, X. Wang and G. He, *Energy Environ. Sci.*, 2023, 16, 2540–2549.
- P. Luo, Y. Wang, W. Zhang, Z. Huang, F. Chao, Y. Yuan, Y. Wang, Y. He, G. Yu, D. Zhu, Z. Wang, H. Tang and Q. An, *Small*, 2025, 21, 2410946.
- K. Wang, T. Qiu, L. Lin, H. Zhan, X.-X. Liu and X. Sun, *Energy Storage Mater.*, 2024, 70, 103516.
- A. M. Elshahawy, Y. Gao, W. Zhao, J. Li, H. Zhang and X. Liu, *Energy Environ. Mater.*, 2025, 0, e70151.
- X. Li, Q. Xu, Z. Liu, J. Chen, H.-B. Xie, S. Chen and J. Liu, *Environ. Sci. Technol.*, 2023, 57, 9975–9983.
- A. N. Rose, E. Hettiarachchi and V. H. Grassian, *J. Colloid Interface Sci.*, 2022, 614, 75–83.
- Y. P. Klapshin, I. A. Solonina, M. N. Rodnikova, M. R. Kiselev, A. V. Khoroshilov and S. V. Makaev, *Mendeleev Commun.*, 2020, 30, 534–536.
- J. Wan, R. Wang, Z. Liu, S. Zhang, J. Hao, J. Mao, H. Li, D. Chao, L. Zhang and C. Zhang, *Adv. Mater.*, 2023, 2310623.
- J. Wang, H. Qiu, Q. Zhang, X. Ge, J. Zhao, J. Wang, Y. Ma, C. Fan, X. Wang, Z. Chen, G. Li and G. Cui, *Energy Storage Mater.*, 2023, 58, 9–19.
- S. Li, Y. Zhong, J. Huang, G. Lai, L. Li, L. Jiang, X. Xu, B. Lu, Y. Liu and J. Zhou, *Energy Environ. Sci.*, 2025, 18, 2599–2609.
- K. Wang, H. Zhan, W. Su, X.-X. Liu and X. Sun, *Energy Environ. Sci.*, 2025, 18, 1398–1407.
- Y. Chen, Z. Deng, Y. Sun, Y. Li, H. Zhang, G. Li, H. Zeng and X. Wang, *Nano-Micro Lett.*, 2024, 16, 96.
- W. Xie, K. Zhu, W. Jiang, H. Yang, M. Ma, L. Zhao and W. Yang, *ACS Nano*, 2024, 18, 21184–21197.
- J. Li, S. Qin, M. Xu, W. Wang, J. Zou, Y. Zhang, H. Dou and Z. Chen, *Adv. Funct. Mater.*, 2024, 2402186.

