

Catalysis Science & Technology

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: F. Zaar, A. Posada-Borbon and H. Grönbeck, *Catal. Sci. Technol.*, 2026, DOI: 10.1039/D6CY00183A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 00.0000/xxxxxxxxxx

Effects of sulfur on dehydrogenation of methylcyclohexane over platinum catalysts[†]

Felicia Zaar,* Alvaro Posada-Borbón, and Henrik Grönbeck*

Received Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

Liquid organic hydrogen carriers (LOHCs) enable storage and transport of H₂ using existing liquid fuel infrastructure, through reversible catalytic hydrogenation and dehydrogenation of organic molecules. A viable, commercially deployed, LOHC system is the methylcyclohexane (C₇H₁₄)/toluene (C₇H₈) system. However, the Pt-based catalysts, which are used for both hydrogenation of C₇H₈ and dehydrogenation of C₇H₁₄, also promote unwanted C-C bond scission, leading to demethylation and LOHC degradation. One route to prevent C-C bond scission over Pt catalysts is to mildly poison the catalyst with sulfur. Using density functional theory (DFT) calculations and mean-field microkinetic modeling, we show that the presence of sulfur, besides suppressing demethylation, also improves the C₇H₁₄ dehydrogenation activity. The enhanced performance is a result of sulfur destabilizing neighboring co-adsorbates, which promotes C₇H₈ desorption. The computational results for dehydrogenation over Pt surfaces reproduce experimental trends for alumina-supported Pt nanoparticles, suggesting that controlled, moderate sulfur poisoning is a universal means to improve the overall performance of Pt catalysts for LOHC dehydrogenation.

1 Introduction

As hydrogen is gaining traction as an energy vector, more practical storage and transport solutions are required for economic viability¹. Liquid organic hydrogen carriers (LOHCs) offer a sustainable and infrastructure-compatible approach to hydrogen storage, enabling reversible incorporation of hydrogen in organic liquids. Several LOHC systems have been explored, including perhydrobenzyltoluene (H12-BT)/benzyltoluene (H0-BT), perhydrodibenzyltoluene (H18-DBT)/dibenzyltoluene (H0-DBT), and methylcyclohexane (C₇H₁₄)/toluene (C₇H₈)^{2,3}. The C₇H₁₄/C₇H₈ system, shown in Fig. 1, has a reasonable hydrogen storage capacity (6.1 wt %), is comparatively inexpensive², and has already been commercialized^{4,5}. However, dehydrogenation of C₇H₁₄ requires high reaction temperatures (approximately 320 °C), opening up the possibility of unwanted side-reactions³. A key challenge is therefore to increase the selectivity of dehydrogenation catalysts.

Hydrogenation and dehydrogenation reactions are commonly performed over Pt-based catalysts. However, Pt also promotes C-C scission, including demethylation³. Interestingly, moderate sulfur poisoning of Pt catalysts has shown to improve the dehydrogenation selectivity of C₇H₁₄⁶ and H18-DBT⁷ over Pt/Al₂O₃, as well as several other reforming reactions^{8–11}. A suggested reason for the enhanced selectivity is that sulfur primarily adsorbs at under-coordinated atoms, effectively blocking these sites^{7,12,13}. Under-coordinated sites are experimentally known to facilitate C-C scission¹⁴, meaning that restricted access to these sites could increase the selectivity toward the desired dehydrogenation reaction.

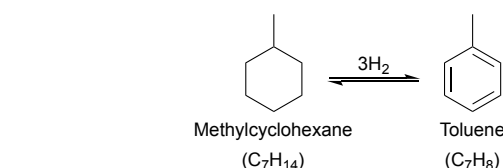


Fig. 1 Investigated LOHC system.

In addition to improving selectivity, sulfur poisoning of Pt/Al₂O₃ has also been reported to enhance the dehydrogenation activity for C₇H₁₄⁶ and H18-DBT⁷. The enhanced activity cannot be explained by poisoning of under-coordinated sites alone, as a maximum in H18-DBT dehydrogenation activity was recorded at the same ratio of accessible metal atoms after sulfur poisoning on three different catalyst samples⁷. This implies that the impact of sulfur on dehydrogenation is not strongly dependent on catalyst surface geometry. As sulfur oxidizes Pt it has been suggested that sulfur thereby modifies the interaction between Pt and other adsorbates^{15,16}. However, the underlying mechanisms and the

Department of Physics and Competence Centre for Catalysis, Chalmers University of Technology, Gothenburg, Sweden. E-mail: felicia.zaar@chalmers.se, ghj@chalmers.se.

[†] Supplementary Information available: Convergence tests, d-band center analysis, additional adsorption energy results, detailed description of micro-kinetic model and additional kinetic results. See DOI: 00.0000/00000000.



consequences for dehydrogenation of C₇H₁₄ are unknown.

Here, we use density functional theory (DFT) calculations to investigate how adsorbed sulfur interacts with co-adsorbates, and how it influences dehydrogenation of C₇H₁₄ and demethylation of C₇H₈. Calculations are performed for flat and stepped surfaces, including Pt(100), Pt(111), Pt(223), and Pt(553). We show that the distribution of adsorbed sulfur depends on the Pt surface and that sulfur exhibits a destabilizing effect on neighboring co-adsorbates. The effect of sulfur on the dehydrogenation reaction is two-fold: by substantially decreasing the adsorption energy of C₇H₈, sulfur i) improves reaction kinetics and ii) prevents demethylation of C₇H₈.

2 Computational methods

2.1 First principles calculations

DFT calculations were performed using the plane-wave Vienna ab initio simulation package (VASP) 6.3^{17–19}, within the generalized gradient approximation (GGA) using the Perdew-Burke-Ernzerhof (PBE)²⁰ exchange-correlation functional. van der Waals interactions were accounted for by the zero-damping Grimme D3 dispersion correction²¹. Spin-polarization was applied to relevant gas phase atoms and molecules, including H, S, C₇H₁₃, C₇H₁₁, and C₇H₉. Valence-core interactions were described by the projector-augmented wave (PAW)²² scheme, treating the following valence electrons explicitly: 1s¹ (H), 2s²2p² (C), 2s²2p⁴ (O), 3s²3p⁴ (S) and 6s¹5d⁹ (Pt).

Pt(100), Pt(111), Pt(223), and Pt(553) surface slabs were constructed using the calculated lattice constant 3.92 Å, which coincides with the experimental value. The Pt bulk calculation was performed by applying a (12 x 12 x 12) k-point grid to the Pt primitive unit cell. *p*(4 x 4) surface cells were used for Pt(100) and Pt(111), whereas *p*(4 x 1) surface cells were used for Pt(223) and Pt(553). All slabs were constructed using five atomic layers, where the bottom two layers were constrained to the bulk positions. Periodic images in the z-direction were separated by at least 15 Å. Following a convergence study of the adsorption energy of CO in an atop configuration on Pt(111), the plane-wave cutoff was set to 450 eV and the k-point density to a (4 x 4 x 1) gamma-centered grid for all surfaces. With these settings, the absolute adsorption energy of CO is converged within 0.04 eV. A denser k-point grid of (8 x 8 x 1) was used when evaluating the electronic densities of states. Gas phase molecules were modeled in a (30 x 30 x 30) Å box, using only the gamma point.

Structural relaxations were performed using a conjugate gradient force optimizer until all forces were converged within 0.01 eV/Å. The convergence criteria of the electronic self-consistent loop was set to 10⁻⁶ eV. First order Methfessel-Paxton smearing of 0.1 eV was applied to all surfaces. Transition states were obtained through the nudged elastic band (NEB) and climbing image tools developed by the Henkelman group²³ using the FIRE²⁴ optimizer with default settings. The bottom two layers of each slab were removed during the NEB calculations, leaving three layers, of which the third was constrained. Trajectories were interpolated using seven images between fully relaxed initial and final configurations. After partial conversion without using the

climbing image scheme, the image immediately following the apparent transition state was selected as the new final state. The new final state was relaxed and a new trajectory involving three-seven images was created. Thereafter, a NEB optimization with climbing image was performed until all forces throughout the trajectory were converged within 0.02 eV/Å. Vibrational modes were calculated for the transition state structure to ensure a saddle point had been reached, identified through the appearance of a single imaginary frequency (or possibly two, if one of them corresponded to a frustrated rotation of methyl). Vibrational frequencies of adsorbates were calculated using the harmonic approximation and central finite differences with 0.015 Å steps.

The adsorption energy of a single adsorbate X in the surface cell was calculated as:

$$E_{\text{ads},X} = E_{X/\text{slab}} - E_{\text{slab}} - E_X(\text{g}) \quad (1)$$

where $E_{X/\text{slab}}$, E_{slab} and $E_X(\text{g})$ are the electronic energies of the modified slab, the pristine slab and the gas phase adsorbate molecule, respectively. The differential adsorption energy was calculated according to:




$$E_{\text{diff},X} = E_{X,nY/\text{slab}} - E_{nY/\text{slab}} - E_X(\text{g}) \quad (2)$$

where n is the number of species Y, $E_{X,nY/\text{slab}}$ is the electronic energy of the slab modified with both X and nY , and $E_{nY/\text{slab}}$ is the electronic energy of the slab modified with nY .

The dehydrogenation reaction from C₇H₁₄ to C₇H₈ was modeled on Pt(111) using a sulfur coverage of 3/16. H was removed from one carbon site of C₇H₁₄ at a time, and the lowest energy configuration was chosen as the C₇H₁₃ species. The same procedure was repeated to obtain C₇H₁₂/Pt(111), C₇H₁₁/Pt(111), C₇H₁₀/Pt(111), C₇H₉/Pt(111) and C₇H₈/Pt(111). Co-adsorption of the carbon-containing molecules with H was investigated by placing H on each available site close to the dehydrogenated atom. The energy landscape for the pristine Pt(111) surface was obtained by structural relaxation after removing sulfur from the corresponding sulfur-modified structures.

2.2 Microkinetic modeling

The reaction kinetics were investigated using a simplified version of the microkinetic mean-field model developed in Ref. 25. In the simplified model, the dehydrogenation of C₇H₁₄ and the demethylation of C₇H₈ were modeled as lumped reactions. The considered reaction network include the following reaction steps:



where * denotes an adsorption site, which can be composed of one or more metal sites. Reaction and adsorption energies for reactions (2.2)-(R6) were obtained from the DFT calculations performed in the present work. Activation energies and partition functions were obtained from Ref. 25. The partition function of the simplified dehydrogenation reaction (2.2) was approximated as the partition function for the dehydrogenation of C_7H_{14} to $C_7H_{13} + H$. The activation energy of the forward reaction (2.2) was taken as the highest activation energy among the dehydrogenation steps. The backward activation energy was taken as the sum of the forward activation energy and the reaction energy (0.68 eV) of . For the lumped demethylation reaction (R2), the partition function and the activation energy were modeled by the first step in C_7H_8 demethylation, as reported in Ref 25. All kinetic parameters of the model are reported in Table S9.

In the microkinetic model, Pt(111) modified with a 0.19 monolayer (ML) sulfur coverage was used as a reference system. Accordingly, a change in the sulfur coverage was represented by a change in the reaction energies. Sulfur was assumed to not compete for sites with the reaction intermediates. The maximum total coverage of carbon-based molecules was fixed to 0.11 ML. The simulations were performed in the temperature range 573–923 K, using $p[C_7H_{14}] = 1.00$ bar, considering 5% conversion to $C_7H_8 + H_2$ and 1% conversion to $C_6H_6 + CH_4$. Further details of the model is given in the Supplementary Information (SI)[†].

3 Results and discussion

3.1 Sulfur adsorption

Adsorption of sulfur was investigated on Pt(100), Pt(111), Pt(223) and Pt(553), considering the adsorption sites indicated in Fig. 2. Sulfur adsorbs preferentially at hollow sites, fcc hollow sites, step edge hcp hollow sites and step edge fcc hollow sites on Pt(100), Pt(111), Pt(223) and Pt(553), respectively (results for Pt(111) and Pt(553) are shown in Fig. 3). The preferred adsorption sites on Pt(100) and Pt(111) agree with experimental findings.^{26,27} It has previously been suggested that sulfur preferably adsorbs at under-coordinated sites on nanoparticles⁷. The adsorption energies with respect to atomic sulfur for the preferred adsorption sites are -6.16 eV on Pt(100), -5.73 eV on Pt(111), -5.56 eV on Pt(223) and -5.67 eV on Pt(553).

The adsorption energy is higher in the fcc site on Pt(111) than at the step edges of both Pt(223) and Pt(553). This is not unexpected, considering that the stepped surfaces are subjected to higher internal compressive strain, and that an increase in strain is associated with a decrease in adsorption energy^{29,30}. Defining strain as the average shift in interatomic distance, relative the equilibrium interatomic distance d_0 in bulk Pt ($(d - d_0)/d_0$), among the Pt atoms coordinated to sulfur at the considered adsorption site, we find that the strain is -0.1% , -1.7% and -2.3% for adsorption in fcc sites on Pt(111), step edge fcc sites on Pt(553) and terrace fcc sites on Pt(553), respectively (see Table 1). There is no obvious trend between the preferred adsorption sites and strain on Pt(553) itself, as variations in, for example, bond length and coordination number will also influence the ad-

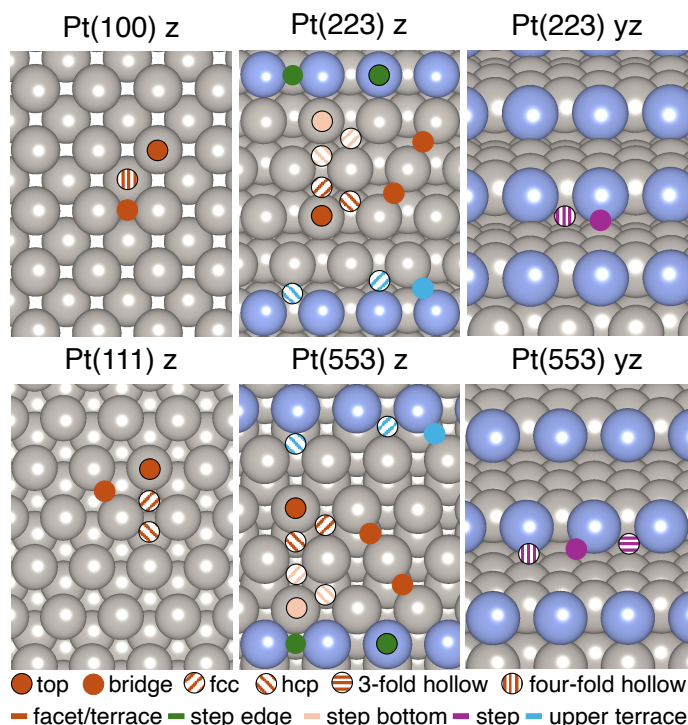


Fig. 2 Investigated adsorption sites on Pt(100), Pt(111), Pt(223) and Pt(553). The letters in the headings indicate the axis or plane along which the image is oriented. The atomic models were made using VESTA²⁸.

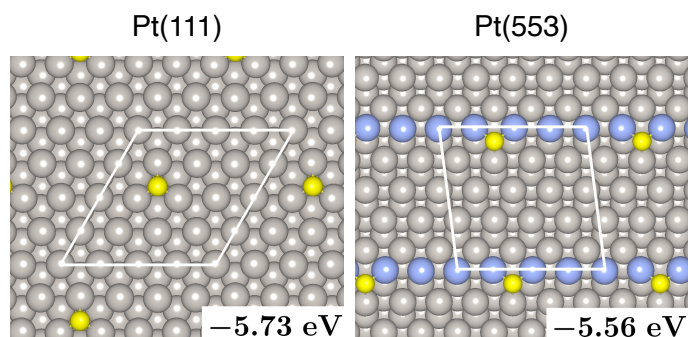


Fig. 3 Adsorption configurations of sulfur on Pt(111) (left) and Pt(553) (right). The adsorption energies are indicated.



sorption energies. However, it is clear that the strain is higher for Pt(553) than for Pt(111). The adsorption energy scales linearly with strain on Pt(111), as shown in the SI[†].

Table 1 Adsorption energies and strain at the considered adsorption sites for sulfur on Pt(111) and Pt(553)

Surface	Adsorption site	E_{ads} (eV)	$\overline{\Delta d/d_0}$ (%)
Pt(111)	fcc	-5.729	-0.1
	hcp	-5.533	-0.1
	top	-3.567	+0.3
Pt(553)	step edge fcc	-5.562	-1.7
	terrace fcc	-5.447	-2.3
	terrace hcp	-5.319	-2.3
	step edge hcp	-5.303	-1.7
	step bottom fcc	-5.216	-1.5
	step three-fold hollow	-5.178	-1.6
	step edge bridge	-5.04	0.0
	step four-fold hollow	-4.751	-1.8

The distribution of sulfur on Pt nanoparticles will depend on how the adsorption energy is affected by strain. On nanoparticles with large terraces, where the local strain approaches that of Pt(111), sulfur would adsorb on the terrace rather than at under-coordinated sites. In contrast, on nanoparticles with small terraces, where the strain is higher, sulfur would primarily adsorb at under-coordinated sites. Consequently, the nature of sulfur poisoning of Pt catalysts – previously often attributed to blocking of under-coordinated sites¹² – depends on the catalyst surface geometry.

The presence of sulfur on the surface will affect the adsorption properties of other adsorbates. In Ref. 7, CO was used as a probe molecule for sulfur adsorption on Pt nanoparticles. Here we investigate adsorption of sulfur and CO on Pt(100), Pt(111), Pt(223), and Pt(553). Considering first only CO adsorption, we find that CO preferentially adsorbs at bridge sites on Pt(100) (-2.49 eV), and at fcc hollow sites on Pt(111) (-2.16 eV). These results are in agreement with previous computational studies at low CO coverages.^{31–35} We note that the adsorption energies are overestimated compared to experiment, according to which the adsorption energy of CO is approximately -1.9 eV on Pt(111)³⁶, and that the experimentally favored top site on Pt(111) is not reproduced. These discrepancies are well-known limitations of using the PBE functional,^{37–39} although the inclusion of van der Waals corrections mitigates the site-ordering error between the top and fcc sites.⁴⁰

CO preferentially adsorbs in step bridge sites (-2.44 eV) and in step top sites (-2.26 eV), on Pt(223) and Pt(553), respectively. As noted above, sulfur also favors adsorption at step edges on Pt(223) and Pt(553), implying that CO and sulfur compete for the under-coordinated sites on these surfaces. This result agrees with the Diffuse Reflectance Infrared Fourier Transform Spectroscopy (DRIFTS) observations of Auer et al.⁷ Upon sulfur exposure, spectral features associated with CO at defect or corner/apex sites disappeared and all CO-related peaks shifted to higher wavenumbers.

The effect of sulfur on CO adsorption can be examined in greater detail by evaluating the CO adsorption energy in different sulfur co-adsorption configurations. On all studied surfaces,

the adsorption energy and preferred adsorption site of CO is unaffected by the presence of sulfur given that CO and sulfur are separated by at least one Pt atom. However, when sulfur and CO are positioned as nearest neighbors, such that they share at least one Pt atom, the adsorption energy of CO decreases on all four surfaces. On Pt(111), sharing the same Pt atom does not correspond to a minimum on the potential energy surface and CO relaxes to a bridge site during the geometry optimization. Similarly, CO moves from its preferred step edge top site to a step edge bridge site on Pt(553). These results are shown in Fig. 4.

The decrease in CO adsorption energy in the immediate vicinity of sulfur is rationalized by the traditional d-band model⁴¹. For both Pt(111) and Pt(553), the d-band centers E_{dbc} of the sulfur-coordinated Pt atoms are shifted to lower energy, by 0.64 and 0.45 eV, respectively (see the SI[†]), which is associated with a weakening of the chemisorption energy of nearby species. Notably, only the d-band centers of the Pt atoms directly bound to sulfur are strongly affected, clearly showing that the effect of sulfur on co-adsorbates is local.

The local character of the electronic influence of sulfur on the Pt surface is further illustrated by the sulfur-induced charge density difference relative the pristine Pt surface, as shown in the bottom panel of Fig. 4. From this analysis, it is evident that sulfur partially oxidizes the Pt surface and that the lateral extension of the effect is limited to the Pt directly bound to sulfur. Although the lateral effect of sulfur is local, the induced charge-density difference normal to the surface extends to the fourth atomic layer of the slab. This is understood considering that it is the d_{yz} , d_{xz} and d_{z^2} orbitals that are involved in bonding to the sulfur orbitals. It is noteworthy that the appearance and spatial extent of the induced charge-density difference are nearly identical on the Pt(111) facet and the step edge of Pt(553).

The spatial extent of the electronic influence determines which sulfur coverage is attainable at under-coordinated sites. The adsorption energy of sulfur at the step edge of Pt(553) is the same for a 25% and a 50 % sulfur coverage of these sites, -5.56 eV. At 75% sulfur coverage, some sulfur atoms must share Pt atoms, which lowers the adsorption energy to -4.94 eV. As the adsorption energy on the terrace of Pt(553) is -5.45 eV, sulfur will start to occupy terrace sites at higher coverages than 50%. Thus, a 50% coverage of the step edge is sufficient to destabilize all co-adsorbates at the step.

3.2 Effect of sulfur on dehydrogenation of C_7H_{14} and demethylation of C_7H_8

3.2.1 Adsorption of C_7H_{14} and C_7H_8 .

The effect of sulfur on the adsorption properties of C_7H_{14} and C_7H_8 was evaluated for Pt(111) and Pt(553). On Pt(111), C_7H_{14} is adsorbed in a slightly buckled configuration in which the carbon ring is positioned above an fcc site and the methyl group is aligned above an hcp site. The adsorption energy for this configuration is -1.49 eV. On Pt(553), C_7H_{14} is adsorbed over an hcp hollow site site at the bottom of the step, with the CH_3 group partially angled toward the step. The adsorption energy is in this case -1.57 eV. These configurations are shown in Fig. 5).



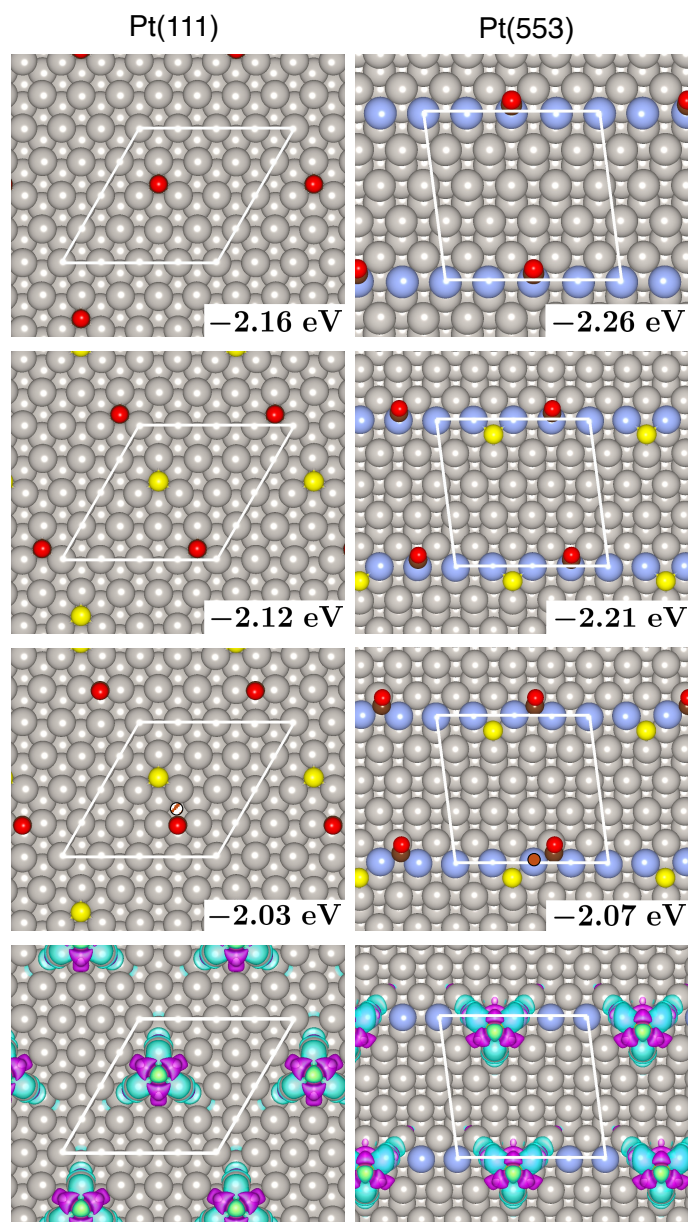


Fig. 4 Adsorption energies and configurations of CO with and without sulfur on Pt(111) [left column] and Pt(553) [right column]. The first row from top shows CO adsorption on pristine Pt. Second (third) row from top shows non-nearest-neighbor (nearest neighbor) configurations of CO and sulfur. The markers in the third row indicate the adsorption sites of CO before structural relaxation. The fourth row shows the sulfur-induced charge density difference relative the pristine Pt surface (isosurface 0.001 \AA^{-3}). Blue and purple indicate electron accumulation and depletion, respectively.




C_7H_{14} is physisorbed on both surfaces, i.e. the bonding is governed by electrostatic and van der Waals interactions. Because C_7H_{14} is physisorbed, sulfur does not significantly impact on its adsorption energy. On Pt(111), the presence of a 1/16 monolayer (ML) of sulfur (corresponding to a single sulfur atom in the supercell) leaves the adsorption energy of C_7H_{14} unchanged, and on Pt(553), a 50% coverage of sulfur along the step edge decreases the adsorption energy from -1.57 eV to -1.51 eV . A coverage of 50% sulfur at the step edge is therefore not enough to change the adsorption site of C_7H_{14} to the terrace of Pt(553), where the adsorption energy is -1.42 eV .

The situation is different for C_7H_8 . On Pt(111), C_7H_8 adsorbs in a bridge configuration similar to the most favorable orientation of benzene on Pt(111)⁴². The molecule is chemisorbed with an adsorption energy of -2.78 eV . The adsorption energy is higher on Pt(553), -3.07 eV . C_7H_8 is in this case preferentially adsorbed at the step with the methyl group aligned along the step edge. In comparison, the adsorption energy at the most stable configuration on the terrace of Pt(553) is -2.40 eV . Thus, C_7H_8 exhibits a strong preference for adsorption at under-coordinated sites, which are known to promote C-C scission.¹⁴

In contrast to the case of C_7H_{14} , sulfur has a notable effect on the adsorption energy of C_7H_8 on both Pt(111) and Pt(553), even if sulfur and C_7H_8 do not share Pt atoms directly. In the studied configuration, C_7H_8 binds to two Pt atoms that are nearest neighbors to sulfur-coordinated Pt sites, resulting in an electronic interaction between chemisorbed C_7H_8 and sulfur mediated through the surface. In the presence of 1/16 ML ($\sim 6\%$) of sulfur on Pt(111), the adsorption energy of C_7H_8 is decreased from -2.78 eV to -2.56 eV . The impact of sulfur on C_7H_8 is also considerable on Pt(553). At a 50% sulfur coverage along the step edge, the adsorption energy of C_7H_8 is decreased from -3.07 eV to -2.24 eV . Consequently, C_7H_8 is less stable at the step in the presence of sulfur than on the terrace of Pt(553). That is, a moderate coverage of sulfur on the step edge could, in principle, change the preferred adsorption site of C_7H_8 to the terrace, where C-C bond scission is less likely. However, as will be discussed below, when taking the entire dehydrogenation reaction into account, the most significant effect of sulfur is that it destabilizes C_7H_8 adsorption and in this way promotes C_7H_8 desorption over demethylation.

3.2.2 Demethylation of C_7H_8 .

Preventing C-C bond scission is relevant at all stages of dehydrogenation. However, the strong preference of C_7H_8 for adsorption at under-coordinated sites warrants a discussion on, in particular, demethylation of C_7H_8 . Focusing on demethylation is further motivated by the fact that desorption of C_7H_8 has proven to be kinetically important for dehydrogenation of C_7H_{14} over Pt(111).²⁵ The demethylation reaction proceeds according to:



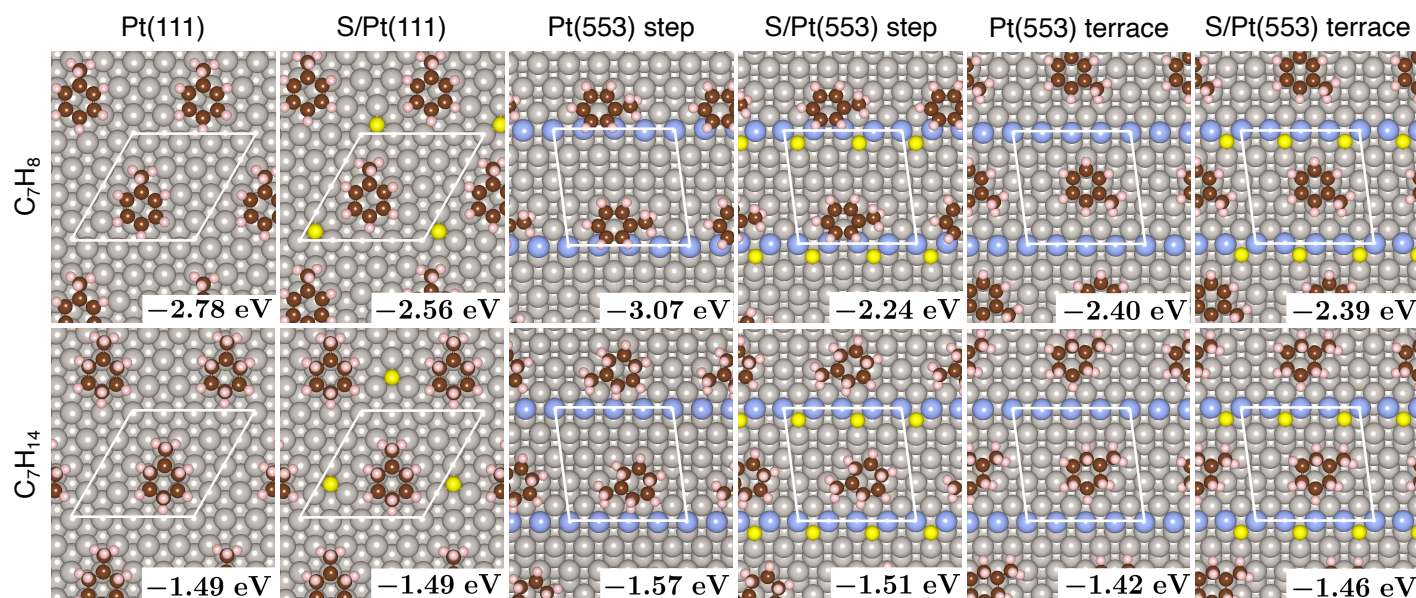


Fig. 5 Adsorption energies of C_7H_8 (upper panel) and C_7H_{14} (lower panel) on pristine and sulfur-modified Pt(111) and Pt(553). Two configurations are shown for Pt(553); the overall most thermodynamically favorable, and the most favorable configuration on the terrace.

Over Pt(111), the first reaction step (R7) is endothermic by 1.21 eV and associated with an energy barrier of 2.26 eV, see Fig. 6. However, the hydrogenation steps make the entire reaction exothermic by -0.73 eV.

Cleaving C_7H_8 to $C_6H_5 + CH_3$ (R7) over Pt(553) is considerably less endothermic than over Pt(111). Over Pt(553), the dissociation is endothermic by 0.69 eV. The difference is mainly attributed to the stabilization of C_6H_5 , which on Pt(553) preferentially adsorbs in an fcc site at the step with the radical center bound to the bottom of the step. CH_3 adsorbs C-down at a top site at the step edge, but its preference for this under-coordinated site over adsorption on the terrace is marginal. In addition to being less endothermic, the first step of demethylation on Pt(553) has a slightly lower barrier than over Pt(111). Three transition states were identified, along the following trajectories: A) rotation of C_7H_8 toward the bottom of the step and CH_3 occupying a top site at the lower terrace after C-C scission; B) rotation of C_7H_8 toward the upper terrace and C-C scission over a bridge site along the edge; and C) rotation of C_7H_8 toward the upper terrace and CH_3 occupying a top site at the upper terrace. The trajectories are shown in the right panel of Fig. 6. The associated activation energies are 2.50 eV, 2.54 eV and 2.20 eV, respectively. Note that additional transition states over Pt(553) with lower barriers may exist that were not captured by the NEB approach. These observations support experimental evidence that C-C scission is favored at under-coordinated sites.¹⁴

3.2.3 Effect of sulfur on dehydrogenation of C_7H_{14} .

The preferential adsorption and demethylation of C_7H_8 on Pt(553) relative to Pt(111) are consistent with experimental observations showing enhanced dehydrogenation selectivity when under-coordinated sites are poisoned by sulfur⁷. In addition to improving selectivity, sulfur poisoning has also been reported to enhance the dehydrogenation activity of H18-DBT⁷ and C_7H_{14} .⁶










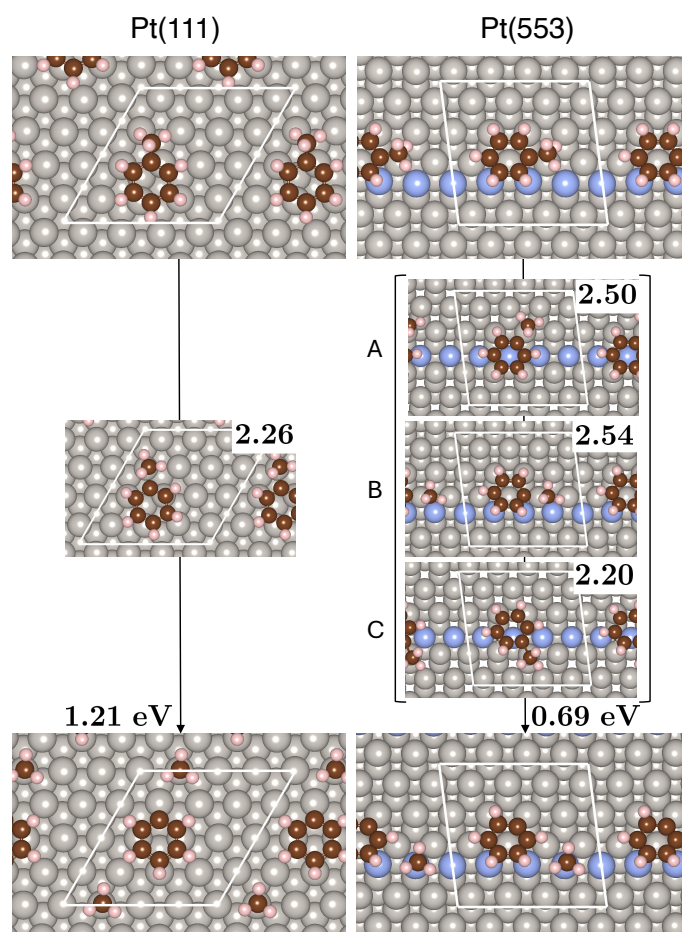


Fig. 6 The first step of demethylation of C_7H_8 over Pt(111) and Pt(553). The upper and lower panels show the most stable configurations of C_7H_8 and $C_6H_5 + CH_3$, respectively. The middle panel shows identified transition states and barrier heights in eV.



Our calculations indicate that C_7H_{14} does not adsorb directly at step sites and that C_7H_8 preferentially binds to facet sites rather than sulfur-poisoned steps. Moreover, as the degree of chemisorption (the number of Pt-C covalent bonds) increases during dehydrogenation from C_7H_{14} to C_7H_8 , the initial adsorption site of C_7H_{14} can be expected to determine the primary reaction site. Consequently, dehydrogenation should preferentially occur on facet sites, and the positive effect of sulfur is likely electronic in nature, arising from sulfur-induced modification of the Pt surface.

Here we considered the full dehydrogenation reaction from C_7H_{14} to C_7H_8 over Pt(111), with a stepwise scission of C-H bonds and desorption of H_2 to the atmosphere:



where, in the case of demethylation, step (R23) is replaced by reaction (R7)-(R9).

Fig. 7 shows the potential energy diagram for C_7H_{14} dehydrogenation, over Pt(111) modified with 3/16 ML sulfur ($\sim 19\%$ of available surface fcc sites), and over pristine Pt(111). The adsorption of C_7H_{14} is close to unaffected by the presence of sulfur. In subsequent reaction steps, sulfur increasingly destabilizes the carbon-containing molecules from physisorbed (C_7H_{14}) to chemisorbed (C_7H_8). Sulfur also increases the reaction energy of the first demethylation step (R7) from 1.28 eV to 1.32 eV, but leaves the activation energy of this step mostly unaffected (2.25 eV vs. 2.26 eV). (We note that the transition state found for the sulfur-modified surface did not fully converge under the chosen criteria, but oscillated by ~ 0.1 eV over the last 100 ionic steps). Desorption of C_7H_8 (R23) is significantly less endothermic in the presence of sulfur (2.18 eV vs. 2.78 eV). Thus, sulfur inverts the preference of steps (R7) and (R23): the first demethylation step (R7) is favored over C_7H_8 desorption (R23) on pris-

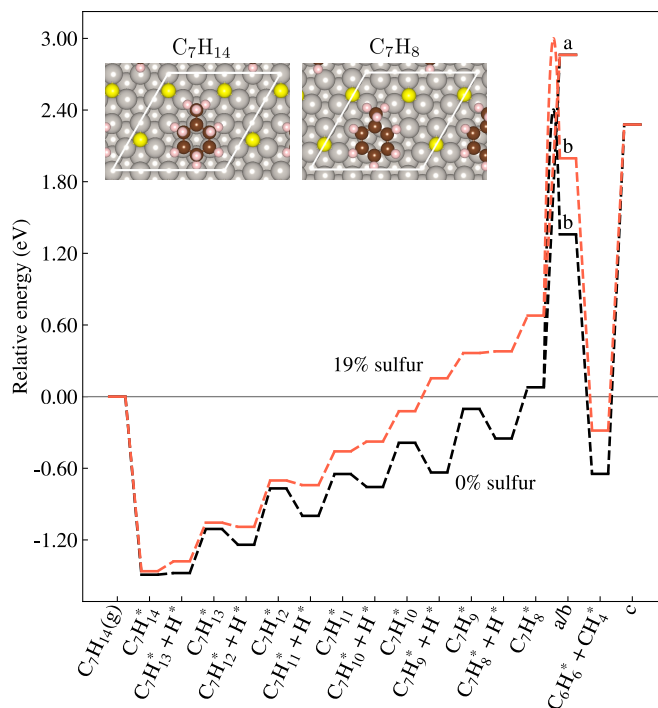


Fig. 7 Dehydrogenation of C_7H_{14} to C_7H_8 and demethylation of C_7H_8 to $C_6H_6 + CH_4$ on Pt(111) in the presence of 0% and 19% S. The insets show the obtained configuration of C_7H_{14} (left) and C_7H_8 (right) on Pt(111) modified with 19% S. Labels a, b and c indicate $C_7H_8(g) + 3H_2(g)$, $C_6H_5^* + CH_3^*$ and $C_6H_6(g) + CH_4(g) + 2H_2(g)$, respectively.

tine Pt(111), whereas the opposite applies on the sulfur-modified surface.

The energy diagram in Fig. 7 displays the purely electronic influence of sulfur on dehydrogenation, as diffusion and rotation beyond what occurred during structure relaxation was not considered for any of the intermediates. In particular for the pristine case, more favorable configurations may exist, as the starting configuration for the optimization was obtained from the sulfur-modified structure. Consequently, the difference in stability between the pristine and sulfur modified surface is underestimated.

The fact that sulfur affects the first and last steps of dehydrogenation differently is beneficial for the reaction kinetics. In Ref. 25 it was demonstrated that decreasing the adsorption energy of C_7H_{14} lowers the turnover frequency (TOF), whereas decreasing the adsorption energy of C_7H_8 increases the TOF. Because sulfur does not alter the adsorption energy of C_7H_{14} but destabilizes C_7H_8 , introducing a small amount of sulfur to Pt(111) should not affect the reaction kinetics of C_7H_{14} adsorption, but likely increase the C_7H_8 desorption rate. Therefore, moderate sulfur poisoning should enhance catalyst selectivity by favoring product desorption over a side reaction, and also improve activity by facilitating a kinetically important step.

It should be noted that modifying the catalyst surface with sulfur introduces a risk of forming SH and subsequently H_2S . However, the formation of SH from $S + H$ is calculated to be endothermic by 1.08 eV (calculated using a $p(3 \times 3)$ surface cell with 5 atomic layers). Interestingly, the endothermicity of the reaction contrasts with the behavior of oxygen and hydrogen, as water is



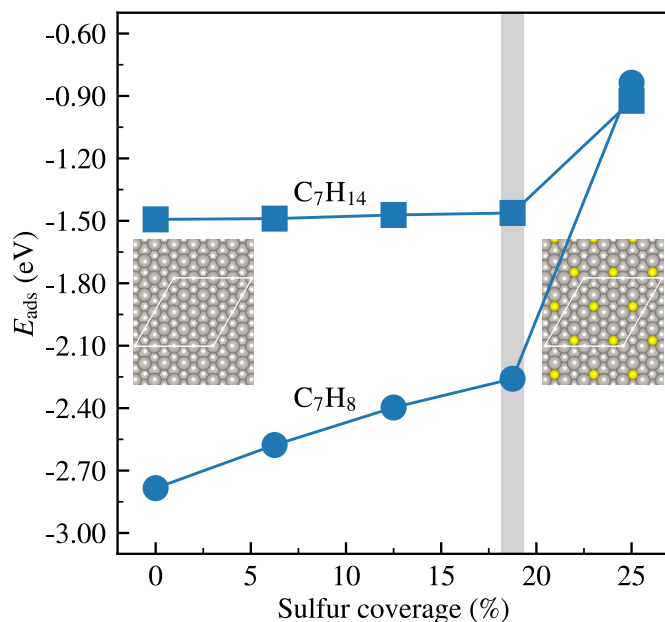


Fig. 8 Adsorption energy of C_7H_{14} and C_7H_8 as functions of sulfur coverage on Pt(111).

known to form on Pt(111).⁴³ The difference is attributed to the larger size of sulfur, which causes sulfur to bind more strongly to the surface than does oxygen – their respective adsorption energies are -4.28 eV and -5.60 eV. This result agrees with previous computational studies showing that H_2S formation is endothermic over Pt(111)⁴⁴, as well as with experimental dehydrogenation of H18-DBT, where no H_2S was detected in the exhaust after catalyst pretreatment in a reducing hydrogen atmosphere⁷.

4 Sulfur coverage and dehydrogenation kinetics

The energy landscape in Fig. 7 was evaluated at a sulfur coverage of 3/16 ML ($\sim 19\%$). This coverage was chosen to have the highest effect on C_7H_8 adsorption, while still allowing adsorption of C_7H_{14} . The coverage dependence of C_7H_8 and C_7H_{14} adsorption is shown in Fig. 8. The adsorption energy of C_7H_8 decreases from -2.78 eV to -2.26 eV when the coverage is increased from 0 to 3/16 ML. The clear coverage dependence originates from the fact that C_7H_8 is chemisorbed on the surface. Conversely, the adsorption energy of C_7H_{14} , which is physisorbed, remains unaffected up to a sulfur coverage of 3/16 ML. At higher sulfur coverages, the molecules cannot access enough metal sites and the adsorption energies decreases significantly.

There is also a limit to the amount of sulfur that can be adsorbed on the surface. At about 5/16 ML ($\sim 31\%$), some sulfur atoms must share metal sites, resulting in a significantly lower average adsorption energy. According to the above discussion on sulfur-induced charge density difference, each sulfur atom can be assumed to prevent co-adsorption on three metal sites. At 4/16 ML (25%), 12/16 ML or 75% of all metal sites on the surface would be effectively blocked by sulfur. This result aligns with the experimental findings by Auer et al.,⁷ suggesting that there is an upper limit to sulfur loading on Pt/ Al_2O_3 corresponding to 26-35% available metal sites.

The 3/16 ML coverage of sulfur used to construct the potential energy diagram in Fig. 7 corresponds to 44% available metal sites. This value agrees well with Ref. 7 where the maximum H18-DBT dehydrogenation activity was achieved at 44-48% available metal sites for all their investigated catalyst samples. In fact, through microkinetic mean-field modeling, we accurately reproduce the experimentally observed activity as a function of accessible metal sites, Fig. 9. Specifically, we find that the TOF increases between 100% and 44% available metal sites, corresponding to sulfur coverages of 0 to 19%. When the sulfur coverage reaches 25%, the TOF decreases dramatically, which coincides with the calculated sulfur-induced drop in adsorption energy of the carbon-based species at this coverage.

The dependence of the TOF on the amount of sulfur on the Pt surface reflects the surface coverages of C_7H_8 and C_7H_{14} , Fig. 9. Here, the coverages are reported with respect to the number of Pt surface sites. The coverage of C_7H_8 decreases with increasing sulfur coverage, whereas the coverage of C_7H_{14} follows the trend in the TOF. In particular, the coverage of C_7H_{14} increases between 0 and 19% sulfur and drops at higher sulfur coverages. The kinetic results highlight that sulfur coverages of up to 19% promotes dehydrogenation activity by facilitating desorption of C_7H_8 , which frees sites for C_7H_{14} adsorption. As we reach the same conclusions as Ref. 7 regarding both maximum and optimum sulfur coverage, using Pt(111) as model surface, we conclude that the most important contribution of sulfur to dehydrogenation performance is not to block under-coordinated sites but rather to electronically modify the Pt surface.

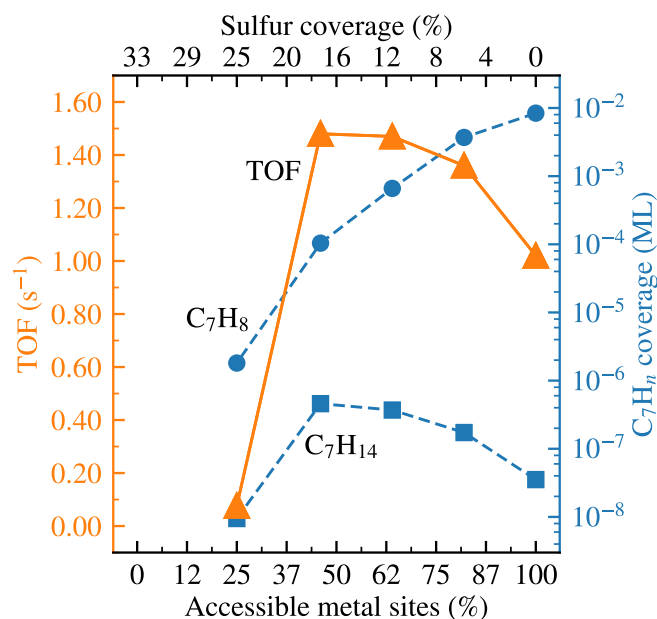


Fig. 9 Maximum TOF as a function of sulfur coverage and the ratio of accessible metal atoms. The simulations were performed using $T = 573 - 923$ K, $p[C_7H_{14}] = 1.00$ bar, 5% conversion to $C_7H_8 + H_2$, 1% conversion to $C_6H_6 + CH_4$, and a saturation coverage of 11% for the carbon-containing species. The maximum TOF is reached at temperatures 817 K, 787 K, 773 K, 769 K and 787 K, from lowest to highest sulfur coverage. Each sulfur atom is assumed to block three metal sites.



Conclusions

We have investigated the effects of under-coordinated sites and sulfur on the dehydrogenation of C_7H_{14} to C_7H_8 over Pt surfaces. The strongest sulfur adsorption energy is obtained on extended Pt(111). On stepped Pt(223) and Pt(553) surfaces, sulfur preferentially adsorbs at under-coordinated sites; however, the adsorption is weaker than on Pt(111). Compressive strain makes the adsorption energies on the (111) micro-facets of Pt(223) and Pt(553) weaker than on Pt(111). Irrespective of surface geometry, sulfur locally modifies the charge density and d-band center of neighboring Pt atoms, thereby reducing the adsorption energies of co-adsorbates in its immediate vicinity.

Sulfur influences the adsorption and reaction properties of C_7H_{14} and C_7H_8 in two main ways. First, in the absence of sulfur, chemisorbed C_7H_8 preferentially adsorbs at step sites, which are also the primary sites for undesired demethylation. By blocking these sites, controlled sulfur poisoning suppresses this side reaction. Second, sulfur reduces the adsorption energy of C_7H_8 approximately linearly as the coverage increases from 0 and 19%. In contrast, C_7H_{14} is physisorbed and preferentially adsorbs on (111) facets, and its adsorption energy is largely unaffected by sulfur up to a coverage of 19%. At sulfur coverages above 19%, the adsorption energies of both C_7H_8 and C_7H_{14} decrease substantially.

The sulfur-induced changes in adsorption and reaction properties have important consequences for the dehydrogenation of C_7H_{14} to C_7H_8 . The primary effects are facilitated C_7H_8 desorption and suppression of demethylation. Our DFT-based mean-field microkinetic model shows that decreasing the C_7H_8 adsorption energy leads to an increased turnover frequency, with a maximum at a sulfur coverage of 19%, corresponding to 44% available metal sites. Our computational results for Pt(111) are consistent with Ref. 7, where H18-DBT dehydrogenation over Pt nanoparticles was found to reach maximum activity at 44–48% available metal sites. Our study suggests that an important effect of adsorbed sulfur is its electronic modification of the catalyst surface. In conclusion, controlled and moderate sulfur poisoning of Pt catalysts prevents LOHC degradation and improves overall catalyst performance.

Author contributions

Felicia Zaar: investigation, formal analysis, visualization, writing – original draft. Alvaro Posada-Borbón: methodology, investigation, writing – review & editing. Henrik Grönbeck: conceptualization, methodology, funding acquisition, supervision, writing – review & editing.

Conflicts of interest

There are no conflicts to declare.

Data availability

Data for this article, including vasprun.xml files for structure relaxations, vibrational modes, charge densities, densities of state and NEB trajectories, are available at Zenodo under accession code⁴⁵ <https://www.doi.org/10.5281/zenodo.18601893>.

Acknowledgements

The Competence Centre for Catalysis (KCK) is hosted by Chalmers University of Technology and is financially supported by the Swedish Energy Agency (52689–1) and the member companies Johnson Matthey, Perstorp, Powercell, Preem, Traton, Umicore, and Volvo Group. Additional support is acknowledged from the Swedish Research Council (2024-05250) and the Wallenberg Initiative Material Science for Sustainability (WISE). The calculations were performed at NSC via a NAISS grant (NAISS 2024/3-26).

Notes and references

- 1 M. Niermann, S. Drünert, M. Kaltschmitt and K. Bonhoff, *Energy Environ. Sci.*, 2019, **12**, 290–307.
- 2 J. Cashel, D. Yan, R. Han, H. Jeong, C. W. Yoon, J. A. Ambay, Y. Liu, A. T. Ung, L. Yang and Z. Huang, *Angew. Chem. Int. Ed.*, 2025, **64**, e202423661.
- 3 P. Preuster, C. Papp and P. Wasserscheid, *Acc. Chem. Res.*, 2017, **50**, 74–85.
- 4 Y. Okada, T. Mikuriya and M. Yasui, *Kemikaru Enjiniyaringu*, 2015, **60**, 187.
- 5 Y. Okada and M. Yasui, *Hyomen Kagaku*, 2015, **36**, 577–582.
- 6 Y. Okada, K. Imagawa and Y. M., *8th Tokyo Conference on Advanced Catalytic Science and Technology (TOCAT8)*, 2018.
- 7 F. Auer, D. Blaumeiser, T. Bauer, A. Bösmann, N. Szesni, J. Libuda and P. Wasserscheid, *Catal. Sci. Technol.*, 2019, **9**, 3537–3547.
- 8 C. Apesteguía and J. Barbier, *J. Catal.*, 1982, **78**, 352–359.
- 9 P. van Trimpont, G. Marin and G. Froment, *Appl. Catal.*, 1985, **17**, 161–173.
- 10 W. J. Doolittle, N. D. Skoularikis and R. W. Coughlin, *Journal of Catalysis*, 1987, **107**, 490–502.
- 11 J. Parera and J. Beltramini, *J. Catal.*, 1988, **112**, 357–365.
- 12 F. Alhumaidan, D. Cresswell and A. Garforth, *Energy Fuels*, 2011, **25**, 4217–4234.
- 13 R. Streber, C. Papp, L. M. P. A., A. Bayer, S. Wickert, M. Schöppke, R. Denecke and H.-P. Steinrück, *J. Phys. Condens. Matter*, 2009, **21**, 134018.
- 14 G. Somorjai and D. Blakely, *Nature*, 1975, **258**, 580–583.
- 15 T. Tri, J. Massardier, P. Gallezot and B. Imelik, *Metal-Support and Metal-Additive Effects in Catalysis*, Elsevier, 1982, vol. 11, pp. 141–148.
- 16 C. Apesteguía, C. Brema, T. Garetto, A. Borgna and J. Parera, *J. Catal.*, 1984, **89**, 52–59.
- 17 G. Kresse and J. Hafner, *Phys. Rev. B*, 1993, **47**, 558–561.
- 18 G. Kresse and J. Furthmüller, *Phys. Rev. B*, 1996, **54**, 11169–11186.
- 19 G. Kresse and J. Furthmüller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 20 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 21 S. Grimme, J. Antony, S. Ehrlich and H. Krieg, *J. Chem. Phys.*, 2010, **132**, 154104.



- 22 G. Kresse and D. Joubert, *Phys. Rev. B*, 1999, **59**, 1758–1775.
- 23 G. Henkelman, B. P. Uberuaga and H. Jónsson, *J. Chem. Phys.*, 2000, **113**, 9901–9904.
- 24 E. Bitzek, P. Koskinen, F. Gähler, M. Moseler and P. Gumbsch, *Phys. Rev. Lett.*, 2006, **97**, 170201.
- 25 A. Posada-Borbón, T. Möslinger and H. Grönbeck, *ChemRxiv*, 2026.
- 26 T. E. Fischer and S. R. Kelemen, *Surf. Sci.*, 1977, **69**, 1–22.
- 27 K. Hayek, H. Glassl, A. Gutmann, H. Leonhard, M. Prutton, S. Tear and M. Welton-Cook, *Surf. Sci.*, 1985, **152-153**, 419–425.
- 28 K. Momma and F. Izumi, *J. Appl. Crystallogr.*, 2011, **44**, 1272–1276.
- 29 M. Mavrikakis, B. Hammer and J. K. Nørskov, *Phys. Rev. Lett.*, 1998, **81**, 2819–2822.
- 30 W. Vanmoerkerke, R. Svensson and H. Grönbeck, *Surf. Sci.*, 2025, **754**, 122678.
- 31 S. Yamagishi, T. Fujimoto, Y. Inada and H. Orita, *J. Phys. Chem. B*, 2005, **109**, 8899–8908.
- 32 K. Doll, *Surf. Sci.*, 2004, **573**, 464–473.
- 33 M. Gajdoš, A. Eichler and J. Hafner, *J. Phys. Condens. Matter.*, 2004, **16**, 1141.
- 34 A. Stroppa, K. Termentzidis, J. Paier, G. Kresse and J. Hafner, *Phys. Rev. B*, 2007, **76**, 195440.
- 35 Z. Yang, R. Wu and J. A. Rodriguez, *Phys. Rev. B*, 2002, **65**, 155409.
- 36 Y. Y. Yeo, L. Vattuone and D. A. King, *J. Chem. Phys.*, 1997, **106**, 392–401.
- 37 P. J. Feibelman, B. Hammer, J. K. Nørskov, F. Wagner, M. Scheffler, R. Stumpf, R. Watwe and J. Dumesic, *J. Phys. Chem. B*, 2001, **105**, 4018–4025.
- 38 R. A. Olsen, P. H. T. Philipsen and E. J. Baerends, *J. Chem. Phys.*, 2003, **119**, 4522–4528.
- 39 K. G. Lakshmikanth, I. Kundappaden and R. Chatanathi, *Surf. Sci.*, 2019, **681**, 143–148.
- 40 P. Janthon, F. Viñes, J. Sirijaraensre, J. Limtrakul and F. Illas, *J. Phys. Chem C.*, 2017, **121**, 3970–3977.
- 41 B. Hammer and J. Nørskov, *Impact of Surface Science on Catalysis*, Academic Press, 2000, vol. 45, pp. 71–129.
- 42 M. Saeys, M.-F. Reyniers, G. B. Marin and M. Neurock, *J. Phys. Chem. B*, 2002, **106**, 7489–7498.
- 43 K. M. Ogle, J. R. Creighton, H. S. Luftman and J. M. White, *J. Chem. Phys.*, 1983, **78**, 5839–5840.
- 44 A. Michaelides and P. Hu, *J. Chem. Phys.*, 2001, **115**, 8570–8574.
- 45 F. Zaar, A. Posada-Borbón and H. Grönbeck, *Effects of sulfur on platinum catalysts for liquid organic hydrogen carriers*, Zenodo, <https://www.doi.org/10.5281/zenodo.18601893>, 2026.



Data availability statement

Data for this article, including vasprun.xml files for structure relaxations, vibrational modes, charge densities, densities of state and NEB trajectories, are available at Zenodo under accession code⁴⁴ <https://www.doi.org/10.5281/zenodo.18601893>, 2026.

References

44 F. Zaar, A. Posada-Borbón and H. Grönbeck, Effects of sulfur on platinum catalysts for liquid organic hydrogen carriers, Zenodo, <https://www.doi.org/10.5281/zenodo.18601893>, 2026.

