

Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: L. Foppa and M. Scheffler, *Faraday Discuss.*, 2026, DOI: 10.1039/D5FD00137D.

Cite this: DOI: 00.0000/xxxxxxxxxx

Rethinking Catalysis: Interpretable AI and Description of Real-World Conditions via Materials Genes[†]Lucas Foppa^{*a,b} and Matthias Scheffler^aReceived Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

Descriptors link basic physicochemical parameters that characterize the materials and the environment to the catalytic performance. Traditionally, descriptors are rooted in mechanistic understanding of elementary surface reactions gained from surface science and atomistic simulations on well-defined surfaces and vacuum. However, real-world catalysis operates under elevated pressures and temperatures, where an intricate interplay of multiple physical processes, including significant materials' restructuring and transport phenomena, governs performance. To bridge this gap, we introduced an interpretable artificial intelligence (AI) approach that identifies key physicochemical parameters correlated with the measured catalytic performance. Analogous to genes in biology and medicine, these "materials genes" provide a statistical description of catalysis without requiring the explicit description of the underlying physical processes. Here, we combine the sure-independence-screening-and-sparsifying-operator (SISSO) symbolic-regression AI approach with a sensitivity analysis based on partial derivatives to determine the most influential genes needed to describe the selectivity of supported palladium-based metal alloy nanoparticles in the hydrogenation of concentrated acetylene streams. The identified genes include the calculated average *d*-band center and the measured average particle diameter, indicating a crucial role of adsorption and structure sensitivity on the formation of ethylene.

1 Introduction

Progress in catalyst design depends on identifying basic physicochemical parameters that characterize materials and correlate with their catalytic performance^{1,2}, a task complicated by the extensive range of variables that can be tuned for creating a new material. These parameters, or functions thereof, establish quantitative relationships with catalytic-performance metrics such as activity or selectivity. We refer to the functions of these physicochemical parameters as *descriptors* hereafter. Traditionally, descriptors are rooted in fundamental understanding of the physical processes governing catalysis. Surface science^{3–8} and *ab initio* atomistic simulations^{9–11} provide detailed information on adsorption and elementary reactions occurring on well-defined model surfaces under vacuum and low temperatures. This knowledge led to descriptors based on adsorption energies of surface intermediates involved in important steps of the catalytic cycle.¹² Adsorption energies offer an intuitive picture of heterogeneous catalysis, as they embody the Sabatier principle¹³ of optimal binding strength. They also relate to activation energy barriers through Brønsted–Evans–Polanyi relationships^{14,15} and to ba-

sic electronic properties of the material through models such as the *d*-band theory.^{16,17} The use of adsorption-energy-based descriptors is convenient for screening new materials,¹⁸ since such quantities can be computed using density functional theory (DFT) calculations. Machine-learning interatomic potentials trained on DFT data further accelerated the screening of materials based on adsorption-energy descriptors.¹⁹ However, descriptors derived from idealized model systems such as adsorption energies are often insufficient to describe the catalytic performance observed under realistic, high-performance operating conditions, characterized by high pressures and temperatures.²⁰ This is because under such realistic conditions, the catalytic performance is governed by an intricate interplay of many physical processes (Fig. 1).^{7,8,21,22} These include not only large and interconnected networks of surface elementary reactions, but also the catalyst's dynamic restructuring and changes of the surface composition during the reaction, mass and heat transport, particle sintering, to name a few. Notably, these physical processes operate across very different time and length scales and are often entangled. Therefore, explicitly modeling the full catalytic progression in order to design a new material is deemed inappropriate. Instead, our goal is to describe the statistical correlation of key physicochemical parameters with the experimental catalyst performance.

Artificial intelligence (AI) offers the strategy for identifying correlations between physicochemical parameters and the mea-

^a The NOMAD Laboratory at the Fritz Haber Institute of the Max Planck Society, Berlin, Germany. E-mail: foppa@fhi-berlin.mpg.de

^b Molecular Simulations from First Principles e.V., Berlin, Germany.

[†] Supplementary Information available. See DOI: 00.0000/00000000.



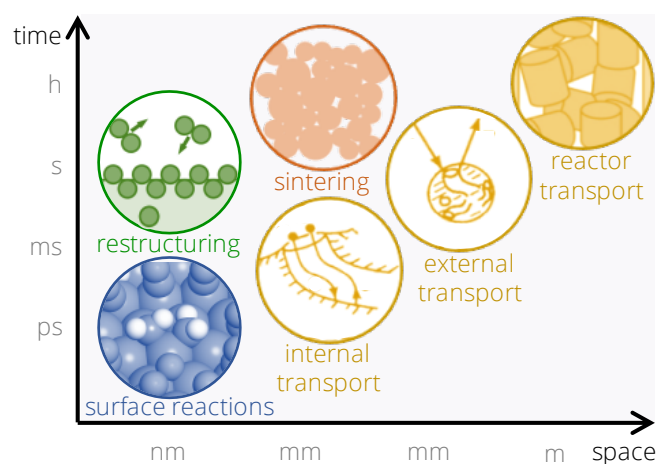


Fig. 1 The performance of real-world heterogeneous catalysts is governed by an intricate interplay of multiple physical processes occurring at extremely different time and length scales. The solid-state chemistry of the material and its restructuring, for instance, is coupled with chemistry of the catalytic reaction, which depends on the surface reaction networks.

sured catalytic performance.^{12,23–27} However, the utilization of experimental data in AI frameworks is complicated by the lack of consistent and well characterized datasets, i.e., datasets created according to rigorous and standardized procedures.^{28–31} To address these limitations, we have developed an interpretable AI approach designed to identify physically meaningful descriptors using *clean* experimental data.^{2,28} The term “clean data” refers to the fact that the materials considered in the AI analysis are carefully synthesized, characterized, and tested according to standardized and well annotated experimental procedures. Indeed, the properties of the material and its catalytic performance are often sensitive to details of the experimental workflow, such as the sequence of synthesis steps and the pretreatment utilized prior to performance testing. Thus, all relevant steps of the workflow should be recorded in detail in order to guarantee the reproducibility of the experiment and well as the consistency of the resulting data.^{28–31} Unlike traditional physics-based models and atomistic simulations, this approach focuses on discovering statistical correlations rather than explicitly simulating all the physical processes, thereby leaving it open what structure or composition the working catalyst has and capturing the complexity of catalysis more effectively. Within this approach, a large set of experimentally measured or calculated candidate descriptive parameters, termed *primary features*, is first chosen. The primary features characterize the materials as well as the reaction environment, e.g., the temperature, pressure, or chemical potential of phase in which reactants and products are contained. They correlate with physical processes that *might* be relevant for the system under consideration. Then, AI is utilized to identify a smaller number of key primary features correlated with the measured catalytic performance, from all initially offered primary features. Crucially, we note that AI identifies potentially nonlinear relationships among multiple primary features. In analogy with biology and medicine, these key primary features are termed *ma-*

terials genes of the catalytic function of interested, e.g., the activity or selectivity.² Thus, the descriptor is a (nonlinear) function of the materials genes. The materials genes correlate with crucial physical processes that trigger, facilitate, or hinder the catalytic function of interest. In view of the high intricacy of these processes, the microscopic relationship between these genes and the catalytic function of interest might be unknown. The concept has been applied to model the catalytic performance in alkane oxidation,^{2,32,33} CO oxidation,³⁴ CO₂ hydrogenation³⁵ and selective hydrogenation of concentrated acetylene streams.³⁶

The Sure Independence Screening and Sparsifying Operator (SISSO) symbolic-regression method^{37,38} gained prominence as a systematic AI approach to identify descriptors in materials science and catalysis.^{39–43} SISSO is well suited for the identification of materials genes in consistent experimental datasets, which often contain a rather small number of materials, e.g., $<10^2$, compared to the number of data points typically used to train AI and machine-learning models, e.g., $>10^4$. In contrast to many widely used AI and machine-learning approaches that interpolate using a fixed predefined descriptor, SISSO automatically identifies descriptors. The descriptors identified by SISSO are *interpretable* in the sense that they depend on a (small) subset of physically meaningful genes, selected from many offered primary features. Additionally, the mathematical relationship between the genes and the target is explicit. Indeed, symbolic-regression methods identify analytical expressions describing the correlations in data.^{44–46} Such interpretability facilitates the extraction of physical insights beyond mere prediction.

In this work, we complement the SISSO approach with a gradient-based partial-effects (PEs)^{47,48} sensitivity analysis to identify descriptors for heterogeneous catalysis and quantify the influence of genes selected in the descriptor expressions (Fig. 2). The approach is illustrated for supported metal nanoparticles (NPs) applied in the selective hydrogenation of concentrated acetylene streams.³⁶ The experimental data utilized here were created and analyzed by a focused SISSO approach in a previous publication.³⁶ Here, we utilize a SISSO model for time-dependent selectivity towards ethylene identified in this previous study in order to demonstrate how the PE sensitivity analysis identifies the most influential genes of a SISSO model thus providing detailed physical insight per material.

2 Methods

2.1 Dataset

The dataset analyzed in this publication can be found in reference³⁶. We analyze metal NPs supported on high-surface-area- α -Al₂O₃. These catalysts were synthesized via mechanochemistry,^{49–52} which is a promising, more atom-efficiency and environmental friendly alternative to wet synthesis methods.⁵³ Nine palladium-based bimetallic alloy NPs are considered: Pd₁Ag₁, Pd₁Ag₅, Pd₁Ag₉, Pd₁Au₁, Pd₁Au₅, Pd₁Au₉, Pd₁Cu₁, Pd₁Cu₅, Pd₁Cu₉. These materials were characterized prior to the reaction by energy dispersive X-ray analysis in a scanning electron microscope (EDX-SEM), transmission-electron microscopy (TEM), and N₂ physisorption. They were tested in the selective hydrogena-



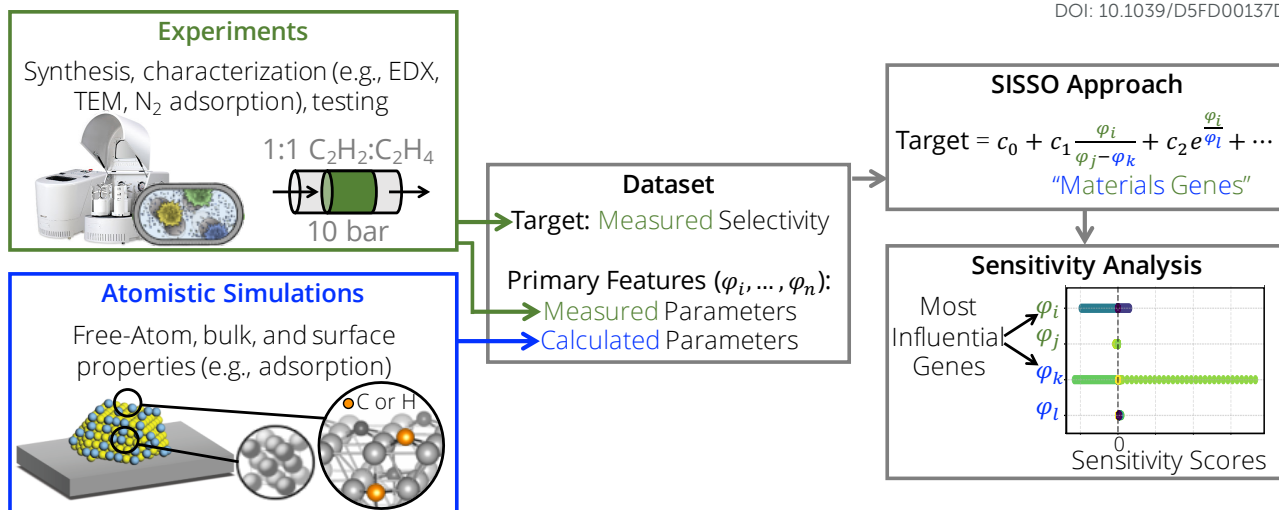


Fig. 2 Interpretable AI approach for the identification of descriptors for heterogeneous catalysis based on data measured experimentally and calculated by atomistic simulations. By using consistent experiments and atomistic simulations on model systems, we create a dataset containing a target materials' function of interest (e.g., selectivity) and many candidate descriptive parameters or primary features that characterize the materials and possibly relevant underlying physical processes. Then the sure-independence screening and sparsifying operator (SISO) symbolic-regression approach identifies analytical expressions correlated with the target and depending on only few of the initially offered primary features. These selected primary features are termed *materials genes*. Finally, the partial effects (PEs) sensitivity analysis pinpoints the genes that most influence the SISO model. Parts of the figure are adapted from reference³⁶.

tion of highly concentrated acetylene streams. The reaction was performed in a steel-lined continuous-flow fixed-bed reactor at 10 bar and 150 °C. The applied feed contained a C₂H₂:C₂H₄:H₂ ratio of 1:1:5 at a weight hourly space velocity of 90,000 cm³ g cat⁻¹ h⁻¹. The feed contained equimolar acetylene-ethylene mixtures, which would result from a hypothetical electric plasma-assisted methane-to-ethylene process. This plasma process can enable the production of ethylene from natural gas, biogas, or hydrogenated CO₂ using the short-term surpluses in electricity from renewable sources.^{54–56} In this process, acetylene is formed as a by-product in equimolar concentrations and it needs to be selectively converted to ethylene in a dedicated, separate downstream process.⁵⁷ Note that the selective hydrogenation of concentrated acetylene streams (> 14 vol.%) is a significantly different catalytic process compared to the selective hydrogenation of acetylene traces (between 0.1 and 2 vol. %), which has been investigated much more extensively.^{54,58–60} Detailed descriptions of the procedures for materials synthesis, characterization, and testing are available elsewhere.³⁶

As an example of target catalytic performance, we analyze the selectivity towards ethylene, denoted $S_{C_2H_4}$. This selectivity was monitored during time on stream (t_{OS}). The dataset contains 539 measurements of $S_{C_2H_4}$, corresponding to 9 materials measured at multiple t_{OS} 's between 0 and 400 minutes (min). We note that the measured $S_{C_2H_4}$ changes significantly with t_{OS} for some of the materials (see below). The SISO modelling aims at describing $S_{C_2H_4}$ for different materials as well as its evolution with t_{OS} during the initial stages of the catalytic process. All $S_{C_2H_4}$ values correspond to materials and reaction conditions resulting in full (100 %) conversion of the reactant acetylene. Thus, the selectivity values can be compared, as they correspond to a fixed conversion of acetylene.

As primary features, we utilized a combination of experimentally measured parameters with parameters calculated using atomistic simulations (Table 1). Four primary features were obtained from the experimental characterization of the materials:^{52,61} the metal loading (w_{metal}), the mean and standard deviation of the particle-diameter distribution (D_μ and D_σ), and the specific surface area (s_{BET}). These primary features correspond to the entire material (NP + support) and they relate metal-support interactions and mesoscale properties of the materials. Noteworthy, these materials' properties are measured before the material is exposed to the reaction environment. Under the reaction, it is possible or even likely that properties, e.g., those related to particle-size distribution, change. In addition to the primary features extracted from the characterization of the materials, we included 3 experimental elemental free-atom properties and 3 experimental bulk properties as primary features reflecting the chemistry of the NP bulk, such as the ionization potential (IP) and the closest interatomic distance (d_{closest}). Those primary features were obtained from tabulated data.^{62–64} t_{OS} is also offered as primary feature in order to capture the time-on-stream dependent behavior of $S_{C_2H_4}$.

The 9 primary features calculated with atomistic simulations reflect the properties of the pristine NP surfaces and the interaction of carbon and hydrogen with the surface and subsurface. These primary features were calculated by DFT with the generalized gradient approximation for electron exchange and correlation (DFT-GGA) considering well-defined low-index model surfaces of previous works.^{65,66} The face-center-cubic crystal structure and its (111) surface was adopted for palladium, silver, and gold. The properties associated to the most stable surface adsorption sites, i.e., the adsorption site corresponding to the highest binding strength, were considered. Examples of calculated



primary features are the energy of the d -band center (ϵ_d), and the binding energy of subsurface hydrogen and carbon ($E_{b,H}^{\text{sub}}$ and $E_{b,C}^{\text{sub}}$, respectively).

The NP elemental, bulk, and surface properties were converted into materials-specific primary features by taking the composition average, indicated by the bar in $\bar{\phi}$, where ϕ is an elemental, bulk, or surface parameter:

$$\bar{\phi} = \sum x_i \phi_i. \quad (1)$$

In Eq. 1, x_i are the nominal molar fractions of each metal in the materials' composition. For instance, $x_{\text{Pd}} = 1/10$ and $x_{\text{Ag}} = 9/10$ for the material based on the supported Pd₁Ag₉ alloy. In total, 20 candidate descriptive parameters were collected, as shown in Table 1.

2.2 The SISO Approach

Starting from the primary features, the SISO approach creates a large pool of expressions, e.g., containing millions of elements, by iteratively applying a predefined set of mathematical operators such as addition, multiplication, logarithm. Then, compressed sensing^{67,68} is used to identify the few D analytical functions, that combined by weighting coefficients provide the best correlation between the selected primary features (genes) and the target property, here the ethylene selectivity $S_{C_2H_4}$. The SISO model has the form

$$S_{C_2H_4}^{\text{SISO}} = c_0 + \sum_{i=1}^D c_i d_i \quad (2)$$

where d_i are the selected functions called *descriptors* and c_i are fitted coefficients. D is referred to as the dimensionality of the descriptor vector. The number of times the mathematical operators are applied (termed *run* and denoted R) and D are hyperparameters of SISO. They control descriptor complexity. In this work, we used the SISO++⁶⁹ code and considered the following mathematical operators, where ϕ_i and ϕ_j are two arbitrary features: ϕ_i , $\phi_i + \phi_j$, $\phi_i - \phi_j$, $\phi_i * \phi_j$, $\frac{\phi_i}{\phi_j}$, ϕ_i^{-1} , $\exp(\phi_i)$, ϕ_i^2 , ϕ_i^3 , $\ln(\phi_i)$, ϕ_i^6 , $\phi_i^{1/2}$, $\phi_i^{1/3}$, and $\exp(-\phi_i)$. The units of the primary features are respected so that, for instance, the operators addition and subtraction are only allowed between features with the same unit. We used a nonlinear optimization during the generation of expressions to include scale and bias terms for the mathematical operations logarithm and exponential.³⁸

A nested five-fold cross validation was used in order to determine the hyperparameters of the SISO model (R and D) and to estimate the predictive performance. In the outer loop of this cross-validation scheme, the dataset is randomly split into five folds with equal size. Each fold is then used as *test set* once, while the remaining four folds are used to train a model. In the inner loop, a new five-fold split is done using the training sets obtained from the first split. Each fold obtained from this second split is used as *validation set* once, while the remaining four folds are used as the training sets. The validation sets are used to determine the hyperparameters of the SISO model. The hyperparameters are chosen such as the root-mean-squared errors (RMSEs) evaluated on the validation sets are minimized. For the

modelling of $S_{C_2H_4}$, we identify $R = 2$ and $D = 3$ as appropriate hyperparameters. The test sets are used to estimate the predictive performance. The distribution of errors evaluated on the test sets indicate a good predictive performance for the modelling of $S_{C_2H_4}$. The mean test error value, for instance, is equal to 0.105. This value is below 25% of the standard deviation of the distribution of $S_{C_2H_4}$ values across the entire dataset. Further details on the application of the SISO approach to model $S_{C_2H_4}$ ³⁶ and on the nested cross validation⁷⁰ are available elsewhere.

2.3 Sensitivity Analysis

The models identified by SISO generally only depend on a few of the initially offered primary features. However, the relative importance of these different genes that appear in a SISO model might differ significantly. Sensitivity analyses identify the most influential input variables of a model.^{69,71–74} Thus, they facilitate the extraction of physical insight and help determining the most promising materials. Sensitivity analyses are referred to as *local* when they provide sensitivity scores per data point (e.g., per material) or *global* when they provide average sensitivity scores for specific data space, e.g., the entire population of materials. Additionally, the sensitivity analysis can be model-specific or model agnostic. Model-agnostic sensitivity analyses examine how changes in an input variable affect the target (output) by systematically modifying the values of the input variables and recording the changes in the model output. The Sobol method, for instance, is a popular model-agnostic global sensitivity analysis^{69,72,75} that decomposes the variance of the model output into contributions from individual input variables and their interactions.

Here, we use the gradient-based partial-effects (PE) sensitivity analysis to assess the impact of genes identified by the SISO approach. The PE method^{47,48,76} quantifies the impact of a given gene in the model's output when the remaining genes are fixed by means of the partial derivative of the model with respect to this gene.^{48,77} This model-specific approach exploits the analytical expressions identified by SISO and provides local sensitivity scores. The local sensitivity analysis is insightful when the physical processes governing the target are significantly different for different groups of materials. In such cases, the contribution of a specific gene might be different for different materials. PEs are less computationally demanding than widely used analyses such as Sobol, since the partial derivative can be obtained analytically.

Let us now apply this concept to $S_{C_2H_4}^{\text{SISO}}$. The partial derivative with respect to gene ϕ_j is:

$$PE_{\phi_j}^{S_{C_2H_4}^{\text{SISO}}} = \frac{\partial S_{C_2H_4}^{\text{SISO}}}{\partial \phi_j}. \quad (3)$$

The higher the magnitude of the PE, the more sensitive is the model to the gene. The sign of the PE indicates whether the relationship between the gene and the target is (locally) directly or inversely proportional. $PE_{\phi_j}^{S_{C_2H_4}^{\text{SISO}}} = 0$ if an initially offered primary feature ϕ_j was not selected in the SISO model. The unit of $PE_{\phi_j}^{S_{C_2H_4}^{\text{SISO}}}$ is the unit of the target divided by the unit of the gene ϕ_j . Thus, $PE_{\phi_j}^{S_{C_2H_4}^{\text{SISO}}}$ values associated to genes having different units



Table 1 Primary features offered in the SISO analysis. These parameters were measured experimentally or calculated with DFT-GGA. They characterize the materials and reaction conditions and they may correlate with possible underlying physical processes.^aComposition averages.^bMeasured before the material is applied in the reaction.

Type	Name	Symbol	Unit	Method
Reaction condition	Time on stream	t_{OS}	min	-
NP+support	Total metal loading (weight fraction) ^b	w_{metal}	-	EDX-SEM ^{52,61}
NP+support	Mean value of particle-diameter distribution ^b	D_{μ}	Å	TEM ^{52,61}
NP+support	Standard deviation of particle-diameter distribution ^b	D_{σ}	Å	TEM ^{52,61}
NP+support	Specific surface area ^b	s_{BET}	m ² /g	N ₂ adsorption ^{52,61}
NP free-atom	Ionization potential ^a	\overline{IP}	eV	Experimental ⁶²
NP free-atom	Electron affinity ^a	\overline{EA}	eV	Experimental ⁶³
NP free-atom	Pauling electronegativity ^a	\overline{EN}	-	Experimental ⁶³
NP bulk ^a	Closest interatomic distance ^a	$\overline{d}_{closest}$	Å	Experimental ⁶⁴
NP bulk ^a	Cohesive energy ^a	\overline{E}_{coh}	eV/atom	Experimental ⁶⁴
NP bulk ^a	Bulk modulus ^a	\overline{B}_0	GPa	Experimental ⁶⁴
NP clean surface ^b	Energy of the <i>d</i> -band center ^a	$\overline{\epsilon}_d$	eV	DFT-GGA ⁶⁶
NP surface with C ^b	Critical surface carbon chemical potential ^a	$\overline{\mu}_C^{surf}$	eV	DFT-GGA ⁶⁵
NP surface with C ^b	Critical subsurface carbon chemical potential ^a	$\overline{\mu}_C^{sub}$	eV	DFT-GGA ⁶⁵
NP surface with C ^b	Distance expansion due to subsurface carbon ^a	$\overline{\delta}_C^{sub}$	Å	DFT-GGA ⁶⁵
NP surface with C ^b	Surface deformation energy due to subsurface carbon ^a	$\overline{E}_{d,C}^{sub}$	eV	DFT-GGA ⁶⁵
NP surface with C ^b	Subsurface carbon binding energy ^a	$\overline{E}_{b,C}^{sub}$	eV	DFT-GGA ⁶⁵
NP surface with H ^b	Surface binding energy ^a	$\overline{E}_{b,H}^{surf}$	eV	DFT-GGA ⁶⁶
NP surface with H ^b	Subsurface binding energy ^a	$\overline{E}_{b,H}^{sub}$	eV	DFT-GGA ⁶⁶
NP surface with H ^b	Work-function change due to hydrogen adsorption ^a	$\overline{\Delta W}_H^{surf}$	eV	DFT-GGA ⁶⁶

are not directly comparable. This is inconvenient when a quantitative comparison among PEs corresponding to different genes that appear in a given model is desired. In order to obtain PEs that can be directly compared across genes which might have different units and scales, we define *scaled partial effects* (SPEs) as

$$SPE_{\phi_j}^{SISO_{C_2H_4}} = PE_{\phi_j}^{SISO_{C_2H_4}} * \sigma_{\phi_j}. \quad (4)$$

In Eq. 4, σ_{ϕ_j} corresponds to the standard deviation of the distribution of ϕ_j values in the entire population, e.g., of materials. In general, such population of materials is practically infinite and unknown. Thus, here we estimate σ_{ϕ_j} using the training data set, assuming that the distributions of primary features in the training set are appropriately described by σ_{ϕ_j} . $SPE_{\phi_j}^{SISO_{C_2H_4}}$ has the unit of the target. Provided that the SISO model expression $S_{C_2H_4}^{SISO}$ is differentiable, the quantities defined in Eq. 3 and 4 are analytical expressions obtained by analytical differentiation. The values of these expressions can be evaluated for each gene or, equivalently, for each data point, providing local sensitivity scores. Global sensitivity scores can then be derived by computing the SPEs for all data points and averaging the results:

$$\overline{SPE}_{\phi_j}^{SISO_{C_2H_4}} = \sum_{i=1}^N \frac{1}{N} |SPE_{\phi_j}^{SISO_{C_2H_4}(i)}|. \quad (5)$$

In Eq. 5, $SPE_{\phi_j}^{SISO_{C_2H_4}(i)}$ are the values of the SPEs evaluated for the *i*-th entry of the training data set and the sum runs over the *N* entries of this data set. The derivatives of SISO models were evaluated using the *sympy* package.⁷⁸ This paper introduces the

PE-based sensitivity approach applied to SISO models. More details about this PE approach and other applications in materials science will be discussed in an upcoming study.⁷⁹

3 Results and discussion

This section summarizes the results for the nine mentioned NP catalysts. We analyze the evolution of ethylene selectivity $S_{C_2H_4}$ with time on stream t_{OS} during the hydrogenation of concentrated acetylene streams at 150 °C. Modeling the evolution of the catalytic performance with t_{OS} allows obtaining insights on the modifications that the materials experience at early stages of the reaction and it allows estimating the time span during which the material can be effectively utilized.

3.1 Measured ethylene selectivity

The values of $S_{C_2H_4}$ range from -1 to 1, as ethylene is both a product of the acetylene selective hydrogenation reaction and part of the reaction feed. Negative $S_{C_2H_4}$ indicates that more ethylene from the feed is consumed than formed from acetylene. Positive $S_{C_2H_4}$ indicates selective materials and conditions. The desired behavior is $S_{C_2H_4} = 1$ or, equivalently, 100% conversion. Diverse performance scenarios ranging from unselective to highly selective are observed among the considered materials and t_{OS} (Fig. 3A). The different catalysts show even qualitatively different performance. The highly selective situations present $S_{C_2H_4}$ values of up to 0.75. In general, the materials containing palladium-silver NPs are the most selective ones, followed by palladium-gold, and palladium-copper. Additionally, different profiles for the evolution of $S_{C_2H_4}$ with t_{OS} are observed depending on the



material. Most of the materials based on the palladium-silver alloys are selective from the start of the reaction, i.e., from $t_{OS} = 0$. For these materials, the selectivity reaches a stable level and then slightly decreases at longer t_{OS} . In contrast, materials containing palladium-gold and, in particular, palladium-copper NPs present constantly increasing $S_{C_2H_4}$ with t_{OS} . The initial selectivity of Pd₁Cu₉, e.g., is $S_{C_2H_4} = -0.89$ but it increases with t_{OS} up to $S_{C_2H_4} = 0.47$ after 365 min. This represents a drastic shift from a completely unselective condition to a highly selective one.

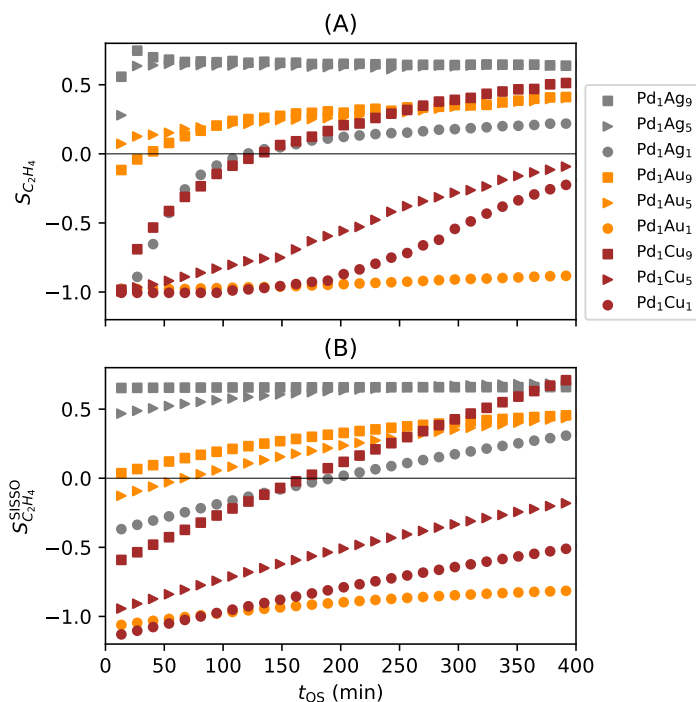


Fig. 3 Experimental results and SISO modelling for the ethylene selectivity in the selective hydrogenation of concentrated acetylene streams catalyzed by palladium-based alloys supported on alumina. (A) Measured $S_{C_2H_4}$ with time on stream. (B) Fit of the SISO model of Eq. 6 ($S_{C_2H_4}^{SISO}$) to the data. Figure adapted from reference³⁶.

3.2 SISO model for ethylene selectivity

SISO was applied to the training dataset containing 539 data points, associated to the 9 materials measured at multiple t_{OS} 's. This dataset contains the measured target $S_{C_2H_4}$ and 20 primary features, including t_{OS} as well as a wide range of measured and calculated parameters characterizing the entire materials and the chemistry of the bulk and surface of the NPs (Table 1). The choice of some of the offered primary features reflects relevant physical processes identified by previous surface science studies and atomistic simulations on model systems. The selectivity towards ethylene depends on the competition between ethylene desorption and its hydrogenation to ethane. Thus, the d -band center¹⁷ is included as primary features, as it correlates with the adsorption of ethylene as well as other intermediates of the acetylene hydrogenation reaction such as vinylidene and ethyl.^{80,81} Additionally, we offer primary features that capture the interaction of NP surfaces with hydrogen, since the availability of surface

hydrogen impacts the rate of ethylene hydrogenation to ethane. Primary features reflecting the interaction of metal surfaces with carbon are also included, as the formation of surface carbides has been shown to be a crucial factor determining the selectivity in palladium systems,^{56,82–88} as it limits the hydrogen availability. Further details on the dataset and SISO approach are given in the Methods section.

The good quality of the fit provided by the SISO model for ethylene selectivity identified in reference³⁶, denoted $S_{C_2H_4}^{SISO}$, is shown in Fig. 3B. This model is able to describe the selectivity of the different materials and its evolution with t_{OS} . The expression of the model is

$$S_{C_2H_4}^{SISO} = c_0 + c_1 \frac{t_{OS}}{\Delta W_H^{surf} * (\bar{\epsilon}_d - E_{b,H}^{surf})} + c_2 (\bar{E}_{d,C}^{sub} * w_{metal} * D_\mu) + c_3 \exp\left\{8.37 * 10^{-4} \frac{eV}{min} \left(\frac{t_{OS} + 366 \text{ min}}{E_{b,H}^{sub} + 1.38 \text{ eV}}\right)\right\}. \quad (6)$$

This model is based on a 3-dimensional descriptor vector. In Eq. 6, $c_0 = -0.098$, $c_1 = -1.22 * 10^{-6} \text{ eV}^2/\text{min}$, $c_2 = 48.491/\text{eV nm}$, $c_3 = -2.65$. The model expression contains t_{OS} , required to describe the time dependency. Additionally, the total metal loading (w_{metal}) and mean value of particle size (D_μ), measured prior to the catalytic test, are also selected by SISO as key experimental gene in Eq. 6. Finally, the following calculated genes are part of Eq. 6: the average d -band center ($\bar{\epsilon}_d$), the average deformation energy of subsurface carbon ($\bar{E}_{d,C}^{sub}$), the average workfunction shift with hydrogen adsorption (ΔW_H^{surf}), the average binding energy of hydrogen ($E_{b,H}^{surf}$), and the average binding energy of subsurface hydrogen ($E_{b,H}^{sub}$). From the initially offered 20 primary features, SISO selected 8 relevant genes to describe the model in different extents. In order to identify the most influential genes of Eq. 6, the PE analysis is applied.

3.3 Sensitivity analysis of the SISO model for ethylene selectivity

The $SPE_{\phi_j}^{SISO}$'s for the 8 genes that were selected by SISO in the expression of the model $S_{C_2H_4}^{SISO}$ are shown in Fig. 4. In this figure, each line corresponds to one gene and each circle corresponds to the $SPE_{\phi_j}^{SISO}$ evaluated for one data points of the training dataset. The circles are colored according to the values of genes. The scale of the x axis is logarithm for a better visualization, as the SPEs have different magnitudes. For the primary features were not selected by SISO in Eq. 6, $SPE_{\phi_j}^{SISO} = 0$. Details on the PE analysis are available in the Methods section.

In order to assess the overall sensitivity of the $S_{C_2H_4}^{SISO}$ model with respect to the genes, we evaluated the mean absolute values of SPEs ($\overline{SPE}_{\phi_j}^{SISO}$) for each gene as a global sensitivity score. The $\overline{SPE}_{\phi_j}^{SISO}$ values are 0.15, 0.12, 0.23, 0.16, 0.75, 0.092, 2.81, and



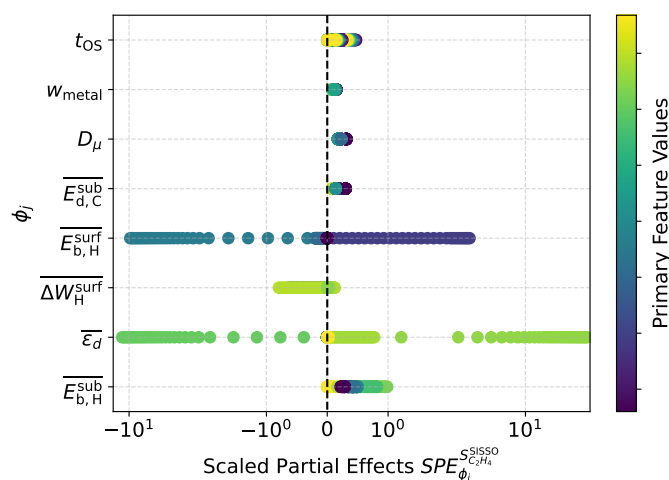


Fig. 4 Sensitivity analysis for the SISO model of ethylene selectivity ($S_{C_2H_4}^{SISO}$) in the selective hydrogenation of concentrated acetylene streams catalyzed by palladium-based alloys supported on alumina. The scaled partial effects $SPE_{\phi_j}^{SISO}$ quantify how influential the genes ϕ_j of the model $S_{C_2H_4}^{SISO}$ are. Each circle corresponds to one data point, associated to one material and one time-on-stream value. The color scale indicates the value of each gene.

0.42 for t_{OS} , w_{metal} , D_{μ} , $\overline{E_{d,C}^{sub}}$, $\overline{E_{b,H}^{surf}}$, $\overline{\Delta W_H^{surf}}$, $\overline{\epsilon_d}$, and $\overline{E_{b,H}^{sub}}$, respectively. Therefore, the relative global influence of the genes to the model decreases as $\overline{\epsilon_d} > \overline{E_{b,H}^{surf}} > \overline{E_{b,H}^{sub}} > D_{\mu} > \overline{E_{d,C}^{sub}} > t_{OS} > w_{metal} > \overline{\Delta W_H^{surf}}$. The most influential gene in the $S_{C_2H_4}^{SISO}$ model (Eq. 6) is the average d -band center $\overline{\epsilon_d}$. This can be related to the key role of physical processes related to the adsorption of reaction intermediates on the NP surface. As shown previously, the alloying of palladium with a second metal downshifts the d -band center, weakening the adsorption of π -bonded species such as ethylene, for instance.^{80,81} Thus, ethylene desorption is favored over its hydrogenation to ethane. The second and third most influential genes are $\overline{E_{b,H}^{surf}}$ and $\overline{E_{b,H}^{sub}}$. They reflect the bond strength between the surface and subsurface with hydrogen. Thus, their high relevance can be related to the availability of surface and subsurface hydrogen and its impact on the rate of hydrogenation of ethylene to ethane, which hinders the formation of the selective-hydrogenation product ethylene.⁸⁹ We note that the values of $\overline{SPE_{\epsilon_d}^{SISO}}$ and $\overline{SPE_{E_{b,H}^{surf}}^{SISO}}$ can be positive or negative depending on the material and t_{OS} (Fig. 4), indicating that the relationships between $\overline{\epsilon_d}$ or $\overline{E_{b,H}^{surf}}$ and $S_{C_2H_4}$ can be directly or inversely proportional. Thus, the adsorption properties can either favor and hinder the selectivity. Finally, the fourth most influential gene D_{μ} could be related to a particle size effect on the ethylene selectivity. Indeed, the size of palladium or copper NPs can significantly affect their selectivity in the hydrogenation of unsaturated bonds by controlling the relative amount of corner and edge sites, which are less coordinated and can thus provide stronger adsorption than the surface sites on closely packed surfaces.^{85,90,91} Thus, D_{μ} correlates with surface sensitivity. The most influential genes identified by the sensitivity analysis confirm the crucial role of the adsorption of π -bonded species and hydrogen in modulating

the ethylene selectivity, as discussed in previous works addressing the hydrogenation of diluted acetylene streams.^{80,81} Additionally, the PEs identify a structure-sensitivity effect, which was only discussed in details for the hydrogenation of dienes.^{85,90,91} The $S_{C_2H_4}^{SISO}$ model is less sensitive to the genes $\overline{E_{d,C}^{sub}}$, t_{OS} , w_{metal} , and $\overline{\Delta W_H^{surf}}$. Thus, the PE analysis indicates a low influence of (sub)surface carbon on the ethylene selectivity for the systems studied here. This indicates that the formation of surface carbides discussed previously in the context of the hydrogenation of diluted acetylene streams might be less relevant to determine the selectivity for the systems considered here.^{56,82–88}

Fig. 5 shows the SPEs for the 4 most influential genes for each of the materials as a function of t_{OS} . The magnitude of the SPE scores associated to the genes $\overline{\epsilon_d}$ and $\overline{E_{b,H}^{surf}}$ is higher for the material based on Pd₁Cu₉ compared to the remaining materials. This difference increases with t_{OS} . This suggests that the impact of physical processes related to adsorption on $S_{C_2H_4}$ is particularly important for this material, especially at long t_{OS} . It can be related to the fact that the Pd₁Cu₉ alloy presents the most drastic change in $S_{C_2H_4}$ with time, as it is a total hydrogenation catalyst at $t_{OS} = 0$ min, but it becomes selective at longer reaction times (Fig. 3). Interestingly, whereas $\overline{SPE_{\epsilon_d}^{SISO}}$ is positive and thus an increase in $\overline{\epsilon_d}$ favors selectivity for Pd₁Cu₉, $\overline{SPE_{E_{b,H}^{surf}}^{SISO}}$ is negative and an increase in $\overline{E_{b,H}^{surf}}$ hinders the selectivity. The SPEs related to the gene $\overline{E_{b,H}^{sub}}$ are relatively insensitive to t_{OS} for most materials. However, the $\overline{SPE_{E_{b,H}^{sub}}^{SISO}}$ values decrease significantly with t_{OS} for the materials based on Pd₁Au₉, Pd₁Au₅, and Pd₁Ag₅, indicating that physical processes related to subsurface hydrogen are only relevant at the beginning of the induction period for these materials. Finally, the analysis of per-material $\overline{SPE_{D_{\mu}}^{SISO}}$ scores shows that the particle-size distribution impacts the copper-based materials, in particular the materials based on Pd₁Cu₉ and Pd₁Cu₅, in a greater extent compared to the remaining materials. This indicates a higher influence of structure-sensitivity for copper-based catalysts. This analysis illustrates how per-data-point, e.g., per-material, SPE scores can be used to obtain insights on the most relevant underlying physical processes for specific data points. In addition to providing global and local, per-data-point physical insights via the identification of the most influential genes in the SISO model, the sensitivity analysis can also be used to design high-throughput materials-screening protocols.⁶⁹ In these protocols, the values of the most influential genes are used to determine rules indicating new materials likely presenting desired target property values, e.g., high values.

The three most influential genes identified by the sensitivity analysis $\overline{\epsilon_d}$, $\overline{E_{b,H}^{surf}}$, and $\overline{E_{b,H}^{sub}}$ are parameters calculated via DFT-GGA calculations for model systems and they highlight the importance of the adsorption properties for catalysis. However, the relevance of the experimental parameter D_{μ} stresses the utility of measured primary features to capture aspects can be hardly included in the theoretical description. Indeed, the distribution of NP sizes is influenced by the properties of the metal alloy as well as by metal-support interactions and synthesis conditions. Addi-



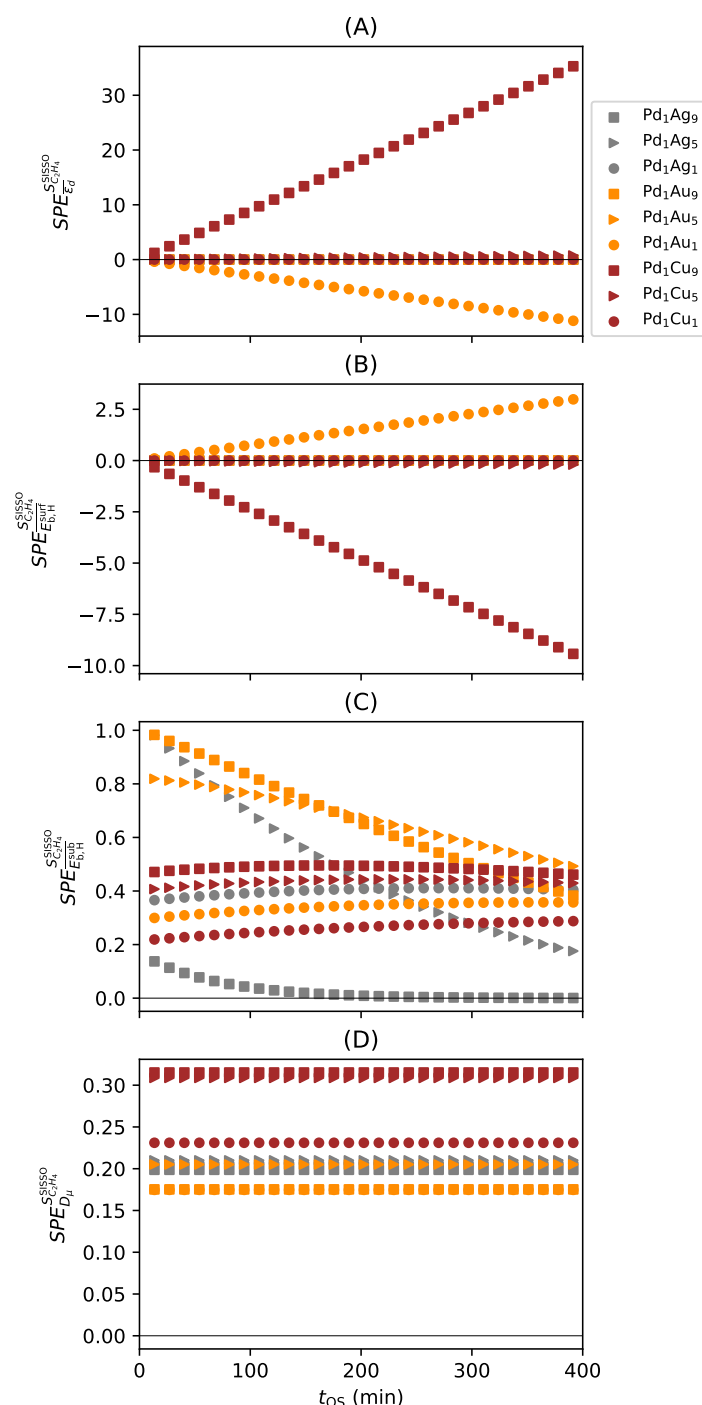


Fig. 5 Evolution of the scaled partial effects $SPE_{\phi_j}^{SIS_{\phi_j}}$ with time on stream (t_{OS}) for the four most influential genes selected by SISSO in the model of Eq. 6 ($S_{C_2H_4}^{SIS}$): \bar{E}_d (A), $\bar{E}_{b,H}^{surf}$ (B), $\bar{E}_{b,H}^{sub}$ (C), D_{μ} (D).

tionally, this distribution might be also modified under the reaction conditions. Modelling all such physical processes by theory is unfeasible. The utilization of materials properties measured under conditions close to reaction conditions, e.g., using *in situ* and *operando* spectroscopy, as primary features was also shown to be crucial in order to capture the catalyst restructuring effect on the catalytic performance.^{2,33} Therefore, the combination of

experimental and theoretical (calculated) primary features is a promising avenue for the identification of descriptors that capture the complexity of heterogeneous catalysis.³⁵ As systematic experimental and theoretical data become available,^{19,92–94} the materials-genes concept offers a framework for integrating surface science, atomistic modelling, and *operando* characterization towards efficient catalyst design.

Finally, we stress that SISSO and the materials genes will only provide reliable descriptions for materials and reaction conditions governed by the same underlying physical processes that govern the performance of the situations in the training set. The reliability of the SISSO models can be assessed and used in order to systematically acquire new data to improve the description for portions of the data space that are not sufficiently covered by the training dataset.⁹⁵ This aspect is discussed in detail in the contribution by Nair *et al.*

4 Conclusions

In this contribution, we propose rethinking the description of heterogeneous catalysis by focusing on statistical correlations identified in experimental and theoretical data generated systematically rather than explicitly modeling all the underlying physicochemical processes and their intricate interplay via atomistic simulations. This approach can capture the intricacy of catalysis more effectively than previous computational approaches, as it does not assume a single underlying physical model. By applying the SISSO approach with the gradient-based PE sensitivity analysis, we identified the most influential basic physicochemical parameters correlated with the selectivity of metal NPs supported on alumina and applied in the hydrogenation of concentrated acetylene streams. These parameters indicate that the adsorption of hydrogen and of molecules containing π bonds modulate the ethylene selectivity. Additionally, a structure-sensitivity effect on the selectivity is captured by the experimentally measured NP size. In addition to the chemical insights, the materials-genes concept enables the design of improved materials and reaction conditions for catalysis.³⁶ In particular, the most influential physicochemical parameters determined by sensitivity analyses can be used to efficiently screen new candidate materials.⁶⁹ The integration of materials genes with automated experiments and large-scale atomistic simulations offers a promising path towards more predictive and generalizable catalyst design.

Author contributions

Conflicts of interest

The authors declare no competing interests.

Data availability

The dataset is available in the Excel supplementary information file of reference³⁶ The SISSO analysis is available at <https://github.com/lfoppa/Focused-AI-SGD-SISSO-acetylene-hydrogenation>.



Acknowledgements

This work was funded by the ERC Advanced Grant TEC1p (European Research Council, Grant Agreement No 740233).

Notes and references

- J. K. Nørskov and T. Bligaard, *Angewandte Chemie International Edition*, 2013, **52**, 776–777.
- L. Foppa, L. M. Ghiringhelli, F. Girgsdies, M. Hashagen, P. Kube, M. Hävecker, S. J. Carey, A. Tarasov, P. Kraus, F. Rosowski, R. Schlögl, A. Trunschke and M. Scheffler, *MRS Bulletin*, 2021, **46**, 1016–1026.
- T. Engel and G. Ertl, *G. Ertl*, Academic Press, 1979, vol. 28, pp. 1–78.
- J. W. Couves, J. M. Thomas, D. Waller, R. H. Jones, A. J. Dent, G. E. Derbyshire and G. N. Greaves, *Nature*, 1991, **354**, 465–468.
- C. T. Campbell, *Surface Science Reports*, 1997, **27**, 1–111.
- G. Ertl, *Angewandte Chemie International Edition*, 2008, **47**, 3524–3535.
- G. A. Somorjai and J. Y. Park, *Angewandte Chemie International Edition*, 2008, **47**, 9212–9228.
- J. M. Thomas, *The Journal of Chemical Physics*, 2008, **128**, 182502.
- K. Reuter, C. Stampf and M. Scheffler, *Handbook of materials modeling: methods*, 2005, 149–194.
- J. K. Nørskov, F. Abild-Pedersen, F. Studt and T. Bligaard, *Proceedings of the National Academy of Sciences*, 2011, **108**, 937–943.
- A. Bruix, J. T. Margraf, M. Andersen and K. Reuter, *Nature Catalysis*, 2019, **2**, 659–670.
- A. J. Medford, A. Vojvodic, J. S. Hummelshøj, J. Voss, F. Abild-Pedersen, F. Studt, T. Bligaard, A. Nilsson and J. K. Nørskov, *Journal of Catalysis*, 2015, **328**, 36–42.
- P. Sabatier, *La catalyse en chimie organique*, C. Béranger, 1920, vol. 3.
- J. Bronsted, *Chemical Reviews*, 1928, **5**, 231–338.
- M. G. Evans and M. Polanyi, *Trans. Faraday Soc.*, 1938, **34**, 11–24.
- B. Hammer and J. Nørskov, *Surface Science*, 1995, **343**, 211–220.
- B. Hammer and J. K. Nørskov, *Advances in catalysis*, 2000, **45**, 71–129.
- J. K. Nørskov, T. Bligaard, J. Rossmeisl and C. H. Christensen, *Nature Chemistry*, 2009, **1**, 37–46.
- L. Chanussot, A. Das, S. Goyal, T. Lavril, M. Shuaibi, M. Riviere, K. Tran, J. Heras-Domingo, C. Ho, W. Hu, A. Palizhati, A. Sriram, B. Wood, J. Yoon, D. Parikh, C. L. Zitnick and Z. Ulissi, *ACS Catalysis*, 2021, **11**, 6059–6072.
- J. Abed, J. Kim, M. Shuaibi, B. Wander, B. Duijf, S. Mahesh, H. Lee, V. Gharakhanyan, S. Hoogland, E. Irtem, J. Lan, N. Schouten, A. U. Vijayakumar, J. Hattrick-Simpers, J. R. Kitchin, Z. W. Ulissi, A. van Vugt, E. H. Sargent, D. Sinton and C. L. Zitnick, *Open Catalyst Experiments 2024 (OCx24): Bridging Experiments and Computational Models*, 2024, <https://arxiv.org/abs/2411.11783>.
- H.-J. Freund, G. Meijer, M. Scheffler, R. Schlögl and M. Wolf, *Angewandte Chemie International Edition*, 2011, **50**, 10064–10094.
- R. Schlögl, *Angewandte Chemie International Edition*, 2015, **54**, 3465–3520.
- L.-H. Mou, T. Han, P. E. S. Smith, E. Sharman and J. Jiang, *Advanced Science*, 2023, **10**, 2301020.
- Z.-J. Zhao and J. Gong, *Nature Nanotechnology*, 2022, **17**, 563–564.
- K. Takahashi, L. Takahashi, S. D. Le, T. Kinoshita, S. Nishimura and J. Ohyama, *Journal of the American Chemical Society*, 2022, **144**, 15735–15744.
- T. Taniike, A. Fujiwara, S. Nakanowatari, F. García-Escobar and K. Takahashi, *Communications Chemistry*, 2024, **7**, 11.
- J. A. Esterhuizen, B. R. Goldsmith and S. Linic, *Nature Catalysis*, 2022, **5**, 175–184.
- A. Trunschke, G. Bellini, M. Boniface, S. J. Carey, J. Dong, E. Erdem, L. Foppa, W. Frandsen, M. Geske, L. M. Ghiringhelli *et al.*, *Topics in Catalysis*, 2020, **63**, 1683–1699.
- A. Moshantaf, M. Wesemann, S. Beinlich, H. Junkes, J. Schumann, B. Alkan, P. Kube, C. P. Marshall, N. Pfister and A. Trunschke, *Catal. Sci. Technol.*, 2024, **14**, 6186–6197.
- D. W. Flaherty and A. Bhan, *Journal of Catalysis*, 2024, **431**, 115408.
- A. C. Alba-Rubio, P. Christopher, M. L. Personick and K. J. Stowers, *Journal of Catalysis*, 2024, **429**, 115259.
- L. Foppa, C. Sutton, L. M. Ghiringhelli, S. De, P. Löser, S. A. Schunk, A. Schäfer and M. Scheffler, *ACS Catalysis*, 2022, **12**, 2223.
- L. Foppa, F. Ruther, M. Geske, G. Koch, F. Girgsdies, P. Kube, S. J. Carey, M. Havecker, O. Timpe, A. V. Tarasov *et al.*, *Journal of the American Chemical Society*, 2023, **145**, 3427–3442.
- G. Bellini, G. Koch, F. Girgsdies, J. Dong, S. J. Carey, O. Timpe, G. Auffermann, M. Scheffler, R. Schlögl, L. Foppa and A. Trunschke, *Angewandte Chemie International Edition*, 2025, **64**, e202417812.
- R. Miyazaki, K. S. Belthle, H. Tüysüz, L. Foppa and M. Scheffler, *Journal of the American Chemical Society*, 2024, **146**, 5433–5444.
- J. M. Mauß, K. S. Kley, R. Khobragade, N.-K. Tran, J. de Bellis, F. Schüth, M. Scheffler and L. Foppa, *ACS Catalysis*, 2025, **15**, 12652–12665.
- R. Ouyang, S. Curtarolo, E. Ahmetcik, M. Scheffler and L. M. Ghiringhelli, *Physical Review Materials*, 2018, **2**, 083802.
- T. A. R. Purcell, M. Scheffler and L. M. Ghiringhelli, *The Journal of Chemical Physics*, 2023, **159**, 114110.
- C. J. Bartel, S. L. Millican, A. M. Deml, J. R. Rumpitz, W. Tumas, A. W. Weimer, S. Lany, V. Stevanović, C. B. Musgrave and A. M. Holder, *Nature Communications*, 2018, **9**, 4168.
- C. J. Bartel, C. Sutton, B. R. Goldsmith, R. Ouyang, C. B. Musgrave, L. M. Ghiringhelli and M. Scheffler, *Science Advances*, 2019, **5**, eaav0693.
- S. R. Xie, G. R. Stewart, J. J. Hamlin, P. J. Hirschfeld and R. G.



- Hennig, *Phys. Rev. B*, 2019, **100**, 174513.
- 42 R. Ouyang, E. Ahmetcik, C. Carbogno, M. Scheffler and L. M. Ghiringhelli, *Journal of Physics: Materials*, 2019, **2**, 024002.
- 43 T. Wang, J. Hu, R. Ouyang, Y. Wang, Y. Huang, S. Hu and W.-X. Li, *Science*, 2024, **386**, 915–920.
- 44 M. Schmidt and H. Lipson, *Science*, 2009, **324**, 81.
- 45 L. Wang, F. Li, Y. Chen and J. Chen, *Journal of Energy Chemistry*, 2019, **28(2)**, 40–49.
- 46 P. Orzechowski, W. La Cava and J. H. Moore, Proceedings of the Genetic and Evolutionary Computation Conference, New York, NY, USA, 2018, p. 1183–1190.
- 47 E. Onukwugha, J. Bergtold and R. Jain, *PharmacoEconomics*, 2015, **33**, 25–30.
- 48 G. S. I. Aldeia and F. O. de França, Proceedings of the Genetic and Evolutionary Computation Conference, New York, NY, USA, 2021, p. 750–758.
- 49 H. Schreyer, R. Eckert, S. Immohr, J. deBellis, M. Felderhoff and F. Schüth, *Angewandte Chemie International Edition*, 2019, **58**, 11262–11265.
- 50 A. P. Amrute, J. De Bellis, M. Felderhoff and F. Schüth, *Chemistry – A European Journal*, 2021, **27**, 6819–6847.
- 51 J. De Bellis, M. Felderhoff and F. Schüth, *Chemistry of Materials*, 2021, **33**, 2037–2045.
- 52 K. S. Kley, J. De Bellis and F. Schüth, *Catalysis Science and Technology*, 2023, **13**, 119–131.
- 53 K. J. Ardila-Fierro and J. G. Hernández, *ChemSusChem*, 2021, **14**, 2145–2162.
- 54 I.-T. Trotaş, T. Zimmermann and F. Schüth, *Chemical Reviews*, 2014, **114**, 1761–1782.
- 55 M. Bowker, S. DeBeer, N. F. Dummer, G. J. Hutchings, M. Scheffler, F. Schüth, S. H. Taylor and H. Tüysüz, *Angewandte Chemie International Edition*, 2022, **61**, e202209016.
- 56 Z. Li, E. Öztuna, K. Skorupska, O. V. Vinogradova, A. Jamshaid, A. Steigert, C. Rohner, M. Dimitrakopoulou, M. J. Prieto, C. Kunkel, M. Stredansky, P. Kube, M. Götze, A. M. Dudzinski, F. Girgsdies, S. Wrabetz, W. Frandsen, R. Blume, P. Zeller, M. Muske, D. Delgado, S. Jiang, F.-P. Schmidt, T. Köhler, M. Arztmann, A. Efimenko, J. Frisch, T. M. Kokumai, R. Garcia-Diez, M. Bär, A. Hammud, J. Kröhnert, A. Trunschke, C. Scheurer, T. Schmidt, T. Lunkenbein, D. Amkreutz, H. Kühlenbeck, V. J. Bukas, A. Knop-Gericke, R. Schlattmann, K. Reuter, B. R. Cuenya and R. Schlögl, *Nature Communications*, 2024, **15**, 10660.
- 57 E. Delikonstantis, E. Igos, M. Augustinus, E. Benetto and G. D. Stefanidis, *Sustainable Energy Fuels*, 2020, **4**, 1351–1362.
- 58 X. Cao, B. W.-L. Jang, J. Hu, L. Wang and S. Zhang, *Molecules*, 2023, **28**, year.
- 59 M. Saliccioli, Y. Chen and D. G. Vlachos, *Industrial & Engineering Chemistry Research*, 2011, **50**, 28–40.
- 60 A. Dasgupta, H. He, R. Gong, S.-L. Shang, E. K. Zimmerer, R. J. Meyer, Z.-K. Liu, M. J. Janik and R. M. Rioux, *Nature Chemistry*, 2022, **14**, 523–529.
- 61 K. K. Kley, *PhD thesis*, Ruhr-Universität Bochum, 2022.
- 62 S. Lias, Linstrom, P.J. and Mallard, W.G., Eds., NIST Chemistry WebBook, NIST Standard Reference Database Number 69, Gaithersburg, USA, 2005.
- 63 *WebElements, howpublished = www.webelements.com, note = Accessed: 2024-10-10.*
- 64 P. Janthon, S. A. Luo, S. M. Kozlov, F. Viñes, J. Limtrakul, D. G. Truhlar and F. Illas, *Journal of Chemical Theory and Computation*, 2014, **10**, 3832–3839.
- 65 P. Sautet and F. Cinquini, *ChemCatChem*, 2010, **2**, 636–639.
- 66 J. Greeley and M. Mavrikakis, *The Journal of Physical Chemistry B*, 2005, **109**, 3460–3471.
- 67 E. J. Candes and M. B. Wakin, *IEEE Signal Processing Magazine*, 2008, **25**, 21–30.
- 68 L. J. Nelson, G. L. W. Hart, F. Zhou and V. Ozoliņš, *Physical Review B*, 2013, **87**, 035125.
- 69 T. A. R. Purcell, M. Scheffler, C. Carbogno and L. M. Ghiringhelli, *Journal of Open Source Software*, 2022, **7**, 3960.
- 70 L. Foppa, T. A. R. Purcell, S. V. Levchenko, M. Scheffler and L. M. Ghiringhelli, *Physical Review Letters*, 2022, **129**, 055301.
- 71 M. D. Morris, *Technometrics*, 1991, **33**, 161–174.
- 72 I. M. Sobol, *Mathematical Modelling and Computational Experiment*, 1993, **1**, 407–414.
- 73 M. Affenzeller, S. M. Winkler, G. Kronberger, M. Kommenda, B. Burlacu and S. Wagner, in *Gaining Deeper Insights in Symbolic Regression*, ed. R. Riolo, J. H. Moore and M. Kotanchek, Springer New York, New York, NY, 2014, pp. 175–190.
- 74 R. M. Filho, A. Lacerda and G. L. Pappa, 2020 IEEE Congress on Evolutionary Computation (CEC), 2020, pp. 1–8.
- 75 S. Kucherenko, S. Tarantola and P. Annoni, *Computer Physics Communications*, 2012, **183**, 937–946.
- 76 E. C. Norton, B. E. Dowd and M. L. Maciejewski, *JAMA*, 2019, **321**, 1304–1305.
- 77 G. S. I. Aldeia and F. O. de França, *Genetic Programming and Evolvable Machines*, 2022, **23**, 309–349.
- 78 A. Meurer, C. P. Smith, M. Paprocki, O. Čertík, S. B. Kirpichev, M. Rocklin, A. Kumar, S. Ivanov, J. K. Moore, S. Singh, T. Rathnayake, S. Vig, B. E. Granger, R. P. Muller, F. Bonazzi, H. Gupta, S. Vats, F. Johansson, F. Pedregosa, M. J. Curry, A. R. Terrel, v. Roučka, A. Saboo, I. Fernando, S. Kulal, R. Cimrman and A. Scopatz, *PeerJ Computer Science*, 2017, **3**, e103.
- 79 L. Foppa and M. Scheffler, *In preparation.*, 2025.
- 80 P. A. Sheth, M. Neurock and C. M. Smith, *The Journal of Physical Chemistry B*, 2005, **109**, 12449–12466.
- 81 T. Yang, Y. Feng, R. Ma, Q. Li, H. Yan, Y. Liu, Y. He, J. T. Miller and D. Li, *ACS Applied Materials & Interfaces*, 2021, **13**, 706–716.
- 82 D. Teschner, J. Borsodi, A. Wootsch, Z. Révay, M. Hävecker, A. Knop-Gericke, S. D. Jackson and R. Schlögl, *Science*, 2008, **320**, 86–89.
- 83 D. Teschner, Z. Révay, J. Borsodi, M. Hävecker, A. Knop-Gericke, R. Schlögl, D. Milroy, S. D. Jackson, D. Torres and P. Sautet, *Angewandte Chemie International Edition*, 2008, **47**, 9274–9278.
- 84 F. Studt, F. Abild-Pedersen, T. Bligaard, R. Z. Sørensen, C. H. Christensen and J. K. Nørskov, *Angewandte Chemie Interna-*



- tional Edition*, 2008, **47**, 9299–9302.
- 85 B. Yang, R. Burch, C. Hardacre, G. Headdock and P. Hu, *Journal of Catalysis*, 2013, **305**, 264–276.
- 86 D. Torres, F. Cinquini and P. Sautet, *The Journal of Physical Chemistry C*, 2013, **117**, 11059–11065.
- 87 B. Yang, R. Burch, C. Hardacre, P. Hu and P. Hughes, *Surface Science*, 2016, **646**, 45–49.
- 88 Y. Liu, F. Fu, A. McCue, W. Jones, D. Rao, J. Feng, Y. He and D. Li, *ACS Catalysis*, 2020, **10**, 15048–15059.
- 89 W. Dong, V. Ledentu, P. Sautet, A. Eichler and J. Hafner, *Surface Science*, 1998, **411**, 123–136.
- 90 O. E. Brandt Corstius, J. van der Hoeven, G. Sunley and P. de Jongh, *Journal of Catalysis*, 2023, **427**, 115103.
- 91 G. Totarella, J. W. de Rijk, L. Delannoy and P. E. de Jongh, *ChemCatChem*, 2022, **14**, e202200348.
- 92 S. Curtarolo, W. Setyawan, G. L. Hart, M. Jahnatek, R. V. Chepulsii, R. H. Taylor, S. Wang, J. Xue, K. Yang, O. Levy, M. J. Mehl, H. T. Stokes, D. O. Demchenko and D. Morgan, *Computational Materials Science*, 2012, **58**, 218–226.
- 93 M. Scheffler, M. Aeschlimann, M. Albrecht, T. Berau, H.-J. Bungartz, C. Felser, M. Greiner, A. Groß, C. T. Koch, K. Kremer, W. E. Nagel, M. Scheidgen, C. Wöll and C. Draxl, *Nature*, 2022, **604**, 635–642.
- 94 L. Barroso-Luque, M. Shuaibi, X. Fu, B. M. Wood, M. Dzamba, M. Gao, A. Rizvi, C. L. Zitnick and Z. W. Ulissi, *Open Materials 2024 (OMat24) Inorganic Materials Dataset and Models*, 2024, <https://arxiv.org/abs/2410.12771>.
- 95 A. S. Nair, L. Foppa and M. Scheffler, *npj Computational Materials*, 2025, **11**, 150.



Data Availability Statement

The dataset is available in the Excel supplementary information file of ACS Catal. 2025, 15, 12652–12665. The SISSO analysis is available at <https://github.com/lfoppa/Focused-AI-SGD-SISSO-acetylene-hydrogenation>.

