

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: M. I. Safa, E. Rahmatizad khajehpasha, J. A. Finkler and S. Goedecker, *Nanoscale Adv.*, 2026, DOI: 10.1039/D6NA00102E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 00.0000/xxxxxxxxxx

Planar Structures of Medium-Sized Gold Clusters Become Ground States upon Ionization

Mohammad Ismaeil Safa^a, Ehsan Rahmatizad Khajehpasha^a, Jonas A. Finkler^a and Stefan Goedecker^{a*}

Received Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

This study investigates the structural stability of ionized gold clusters of sizes ranging from 22 to 100 atoms, contrasting compact, cage and planar structures. While it is well known that neutral clusters in the upper part of this size range predominantly favor compact structures, our results reveal that positively ionized gold clusters exhibit structural transitions in which planar structures become energetically preferred once the charge is sufficiently large. In addition, we study the finite-temperature stability of the structures and find that thermodynamic effects further stabilize planar structures relative to their compact counterparts. To explore the potential energy surface, we use the Minima Hopping algorithm combined with a machine-learned potential. Since the machine-learned potential does not apply to ionized clusters, we introduce a charge-correction term to incorporate Coulomb interactions and charge screening.

1 Introduction

Extensive experimental and theoretical studies show that small gold clusters exhibit a preference for planar (2D) structures up to a critical size, beyond which three-dimensional (3D) compact structures, (i.e. structures which can not host an extra endohedral atom), become energetically favorable^{1–4}. For anionic clusters, photoelectron spectroscopy, ion mobility measurements and Density Functional Theory (DFT) calculations consistently show that clusters remain planar up to Au_{11} , with a structural transition occurring at Au_{12} where planar and 3D isomers coexist and clusters of $Au_{n \geq 13}$ are 3D geometries^{1,3,5,6}. DFT predictions for the 2D to 3D crossover in neutral clusters are strongly method-dependent: Local Density Approximation (LDA) favors a transition at Au_7 , whereas Generalized Gradient Approximation (GGA) with scalar-relativistic can stabilize planar motifs up to Au_{11} ⁷. Cage motifs emerge for Au_{10} – Au_{14} , followed by a transition to compact structures at Au_{15} ⁴. Finite-temperature free-energy calculations using van der Waals-corrected DFT predict that $Au_{9,10}$ remain planar at 100 K, whereas Au_{11} adopts a non-planar capped trigonal prism with D_{3h} symmetry; increasing temperature generally shifts populations toward non-planar structures for Au_8 – Au_{13} , with Au_{11} being a notable exception due to many accessible near-degenerate planar isomers⁸. A recent machine-learning-based global search

has further refined this picture by systematically investigating Au_2 – Au_{55} clusters, identifying the planar to 3D transition at Au_{14} and a subsequent cage to core-shell transformation for $Au_{n \geq 26}$ ⁹. These results not only confirm earlier DFT-based trends but also provide a comprehensive, size-resolved structural map, including several previously unreported low-energy isomers for Au_{13} and Au_{15} – Au_{18} . Additionally, photoelectron spectroscopy and global search studies revealed that anionic clusters Au_{16}^- – Au_{18}^- can also form experimentally detectable cages¹⁰. A paradigmatic example is Au_{20} , which adopts a tetrahedral structure, experimentally confirmed via photoelectron spectroscopy, shown to be a slightly distorted fragment of the bulk fcc lattice with remarkable stability due to its large HOMO-LUMO gap and high electron affinity¹¹. For Au_{26} and Au_{26}^- , global searches reveal a fluxional character. Many distinct minima are only ~ 0.5 eV above the putative ground state and are separated by low barriers. In addition, the predicted ground state motif depends on the exchange-correlation (XC) functional: LDA favors filled-cage core-shell structures for Au_{26} and Au_{26}^- , whereas Perdew–Burke–Ernzerhof (PBE)¹² stabilizes an empty cage for Au_{26} and a tubular motif for Au_{26}^- ¹³. In line with this picture, high-level coupled-cluster benchmarks for Au_{27}^q already reveal an extremely shallow Potential Energy Surface (PES) with many quasi-degenerate compact and non-compact isomers and a strong XC functional dependence of the predicted ground state¹⁴. For Au_{32} , a cage with icosahedral symmetry satisfying the $2(N+1)^2$ spherical aromaticity rule¹⁵ and exhibiting a large HOMO–LUMO gap is proposed as a “golden fullerene”¹⁶. Stability, arising from aromaticity and a large HOMO-LUMO gap, was also found for Au_{50} , where a DFT-based comparison of cage and compact structures found that a cage with D_{6d} was the global

^a Department of Physics, University of Basel, Klingelbergstrasse 82, CH-4056 Basel, Switzerland.

Corresponding author E-mail: stefan.goedecker@unibas.ch

Electronic supplementary information (ESI) available. See DOI: XX.XXXX/XXXXXXXXXX.



minimum^{17,18}. Au_{42} with icosahedral and Au_{60} with chiral icosahedral symmetry cages are typically slightly higher in energy than compacts, remain structurally robust local minima and can act as components in nested or multi-shell clusters^{19,20}. A study based on icosahedral-inspired templates showed that large quasi-icosahedral cages such as Au_{92} and Au_{122} , although not global minima, are low-lying energy metastable structures with high symmetry and strong metallicity²¹. Clusters in the $Au_{n\sim 100}$ size range are compact, and entirely different structural motifs—such as icosahedral, decahedral, or octahedral—can be nearly degenerate in energy. As a consequence, the ground-state structural motif can change upon the addition of a single atom, and the ground-state structure oscillates among these motifs with increasing cluster size²².

While early studies primarily focused on small clusters and their transition from planar to compact geometries, recent experimental studies have demonstrated that atomically thin, free-standing gold monolayers can be synthesized using ligand-assisted self-assembly²³, intercalation beneath graphene²⁴, exfoliation from layered precursors²⁵ and in-situ dealloying inside electron microscopes^{26,27}. These monolayers exhibit remarkable thermal stability, metallic conductivity, and even magnetic edge states in nanoribbons. Moreover, studies based on DFT predicted that hexagonally close-packed 2D gold is dynamically²⁸ and thermodynamically²⁹ stable. Systematic DFT calculations indicate that graphene pores can stabilize free-standing 2D metal patches up to $\sim 8 \text{ nm}^2$, and identify Au as one of the most promising elemental metals for forming stable pore-confined 2D phases³⁰. Complementary computational simulations using ab-initio and molecular dynamics methods further reveal unique behaviors such as 2D liquid phases³¹, strain-induced electronic transitions²⁴, and strong environment-dependent catalytic activity^{32–34}. These findings establish that planar gold structures are not restricted to small clusters but constitute a broader and experimentally realizable class of 2D materials.

These results collectively suggest that planar and cage motifs represent an important class of stable and potentially synthesizable configurations for medium-sized and large gold clusters. We therefore explored whether positive ionization, hereafter referred to simply as ionization, of electron-rich gold clusters provides a route to stabilizing planar or cage motifs. The rationale is based on the assumption that the positive charge is distributed over all atoms, leading to a repulsion between the ionic nuclei. Hence, the electrostatic energy will be smaller in a planar or cage structure, where the number of nearest neighbors is smaller than in compact structures. To test this hypothesis, we systematically investigated the PES of ionized gold clusters ranging from Au_{22} to Au_{100} . For this purpose, we employed the Minima Hopping (MH) algorithm³⁵.

Our approach uses the Atomic Simulation Environment (ASE)-integrated implementation of MH³⁶ and Symmetry-biased MH³⁷. We used machine-learned potentials to evaluate the energies and forces during the MH exploration, with a physically motivated charge-correction term introduced to account for Coulombic repulsion and charge-screening effects in the ionized gold clusters considered here. Notably, our results reveal that planar geometries

emerge as ground state configurations for certain ionization levels, suggesting that ionization can play a pivotal role in stabilizing non-compact cluster morphologies. Furthermore, we account for vibrational contributions to the free energy at finite temperatures. Since atomic vibrations are always present at non-zero temperatures, the vibrational free energy term can affect structural stability. Our calculations indicate that the vibrational free energy contribution at finite temperature further stabilizes planar geometries over compact counterparts. This suggests that, in addition to electrostatic effects, thermal fluctuations also promote the emergence of planar structures at room temperature.

2 Methods

2.1 Global structure search with MH and machine-learned potentials

The exploration of the PES for neutral and ionized gold clusters was carried out with the MH algorithm. MH alternates short molecular-dynamics escape moves and local geometry relaxations, while an adaptive temperature scheme controls the kinetic energy used in the escape steps, which makes it well-suited for sampling complex, high-dimensional PES and locating low-energy minima while avoiding excessive revisits of already known structures. In all MH simulations, the interatomic forces and energies were calculated by machine-learned interatomic potentials rather than by DFT, allowing us to perform extensive global searches for cluster sizes up to Au_{100} .

As a primary PES model, we employed Neural Equivariant Interatomic Potential (NequIP)³⁸, an $E(3)$ -equivariant neural network potential that we trained on DFT reference data for gold clusters. With this potential, we could find all previously known neutral cage structures. By construction, this potential does not explicitly include electrostatic contributions associated with ionization. To extend its applicability to ionized clusters, we augmented NequIP with an electrostatic correction term that is added to both the total energy and the atomic forces.

We assumed that, upon ionization, the charge is uniformly distributed over all atomic sites, such that each nucleus carries an effective charge Q_{tot}/n , where Q_{tot} is the total cluster charge and n is the cluster size. In our first attempt, we added a bare Coulomb interaction between these point charges on top of the NequIP outputs, but this unscreened correction overestimated the effect of ionization and did not reproduce the DFT trends for ionized clusters. We therefore introduced a screened interaction with an exponential damping factor to mimic charge screening and finite-size effects in the metallic cluster. The resulting energy correction term in atomic units takes the form:

$$E = \frac{1}{2} \sum_i \sum_j \frac{Q_{tot}^2}{nr_{ij}} \exp\left(-\frac{r_{ij}}{\lambda}\right), \quad (1)$$

where r_{ij} is the distance between atoms i and j , and λ is an effective screening length that determines how rapidly the correction term decays with interatomic distance. Its value was obtained empirically by fitting to DFT reference energies for even-sized ionized Au clusters from Au_{22} to Au_{100} and ionization levels in the range of $+2e$ to $+10e$ in steps of $2e$, resulting in an opti-



mal global value of $\lambda = 2.64 \text{ \AA}$. The corresponding interatomic forces are then the negative gradient of this energy. The exponential damping takes into account screening effects, leading to a smoother and more physical description of nuclear repulsion inside the cluster. In all MH simulations, these correction terms were evaluated on-the-fly and added to the underlying NequIP energies and forces, so that the search is effectively performed on a charge-corrected PES.

Alongside the charge-corrected NequIP-based PES, we employed a pretrained MACE foundation model³⁹ as a complementary machine-learned potential. Unlike NequIP, which was trained on our own dataset containing compact, cage, and planar structures and then augmented with the charge-correction term, the MACE model was not retrained on our dataset and did not include an explicit charge correction. We therefore did not use MACE on the same footing to describe ionized clusters. Instead, we performed separate MH simulations with MACE mainly to generate additional candidate structures, in particular compact motifs.

The low-energy structures obtained with NequIP and MACE were subsequently validated with DFT, providing evidence that the emergence of cage and planar ground states is not an artefact of machine-learned potentials.

2.2 DFT Calculations

A large number of low-energy compact, cage and planar structures from MH outputs were selected to be validated by DFT. To accurately evaluate the energies and structural properties of ionized gold clusters, we performed DFT calculations using the FHI-aims package⁴⁰. FHI-aims employs an all-electron, numeric atom-centered Gaussian basis set, allowing for highly accurate electronic structure calculations. Relativistic effects are treated by the AZORA method⁴¹.

We employed three XC functionals to validate the robustness of the structural trends: PBE, its solid-state revision, PBEsol, combined with a many-body dispersion correction (PBEsol+MBD), both within the GGA framework; and r^2 SCAN within the meta-GGA framework.^{12,42–44}

We employed the "tight" basis set to ensure high numerical accuracy in describing the electronic structure and treated all clusters using free boundary conditions, simulating isolated gas-phase systems without periodic constraints. Performing structural relaxations for neutral clusters and ionization levels up to $+13e$ enabled us to analyze how increasing ionization drives structural transitions. We set the structural-optimization convergence threshold such that the force norm on each atom falls below 5 meV/\AA . These calculations provide reference data for benchmarking the machine-learned potentials and analyzing charge-dependent structural transitions in gold nanoclusters.

3 Results

In this study, we examined how the structures of gold clusters evolve with increasing ionization. As the ionization level increases, gold clusters show a tendency to form non-compact structures either in the form of a cage or of a planar structure. For

selected Au_n clusters with $n \leq 100$ atoms, we successively increased the ionization level until we could observe a transition of the ground state structure into a cage or planar structure. To characterize the stability of these ionization-induced ground states, we also analyzed the structural energy gap, defined here as the energy difference between the global minimum and the first metastable structure. A larger structural energy gap indicates a stronger energetic stabilization of the corresponding non-compact ground state. While a tendency to form planar structures upon ionization is always observed, different XC functionals predict different threshold ionizations for this transition. The results for the three widely used XC functionals we employed are presented below.

3.1 PBE

We employed PBE, a widely used non-empirical semilocal GGA XC functional. Among the three XC functionals considered in this work, PBE requires the lowest ionization level to stabilize non-compact motifs as ground states. In the neutral clusters, cage geometries are obtained as ground states for Au_n with $n = 22, 24, 26, 27, 28, 30, 32, 48$, and 50 . Upon weak ionization, cages become the ground state for Au_{29}^{+1} , Au_{34}^{+2} , Au_{36}^{+4} , Au_{38}^{+4} , Au_{42}^{+4} , Au_{52}^{+4} , Au_{54}^{+2} and Au_{55}^{+3} . At intermediate ionization level, cage ground states are found for Au_{76}^{+6} , Au_{78}^{+6} , and Au_{80}^{+6} . All remaining clusters favor planar structure as their ground state structures at the corresponding ionization levels. For the planar ground states, the structural energy gaps are as follows: Au_{70}^{+8} , Au_{72}^{+8} , Au_{74}^{+8} fall between 4-5 eV; Au_{82}^{+8} , Au_{84}^{+8} , Au_{86}^{+8} fall between 3-4 eV; Au_{44}^{+6} , Au_{46}^{+6} , Au_{61}^{+7} , Au_{65}^{+7} , Au_{90}^{+8} , Au_{92}^{+8} , Au_{94}^{+8} , Au_{96}^{+8} and Au_{98}^{+8} fall between 2-3 eV; Au_{56}^{+6} , Au_{75}^{+7} and Au_{100}^{+8} fall between 1-2 eV; all remaining cases fall between 0-1 eV. The detailed PBE relative energies and ground state assignments as a function of size and ionization level are shown in fig. 1; the total energy of the lowest energy compact, cage and planar structures are shown in Table SII supplementary information.

3.2 PBEsol+MBD

PBEsol is a semi-local GGA XC functional tailored for solids, and the MBD adds an explicit many-body dispersion correction. We performed separate relaxations of the same structural candidates to determine, for each size, the smallest ionization level at which a planar structure becomes the global minimum. The ionization level required for planar structures to become ground states is generally higher than that predicted by the other two XC functionals, while the corresponding structural energy gaps are as follows: Au_{85}^{+12} with 4.29 eV has the largest structural energy gap; Au_{42}^{+9} , Au_{44}^{+9} , Au_{60}^{+10} , Au_{62}^{+10} , Au_{75}^{+11} and Au_{76}^{+11} fall between 3-4 eV; Au_{48}^{+9} , Au_{55}^{+10} , Au_{56}^{+10} , Au_{61}^{+10} , Au_{65}^{+10} and Au_{78}^{+11} fall between 2-3 eV; Au_{24}^{+7} , Au_{27}^{+7} , Au_{37}^{+8} , Au_{40}^{+8} , Au_{50}^{+9} , Au_{64}^{+10} and Au_{68}^{+10} fall between 1-2 eV; all remaining cases fall between 0-1 eV. This XC functional does not favor cage motifs at all; whenever the planar structures become ground state, the cages are higher in energy than compacts. In the table 1, the ionization levels required for each cluster size are reported. The resulting energetic ordering is shown in fig. 2. The total energy of the lowest energy compact, cage



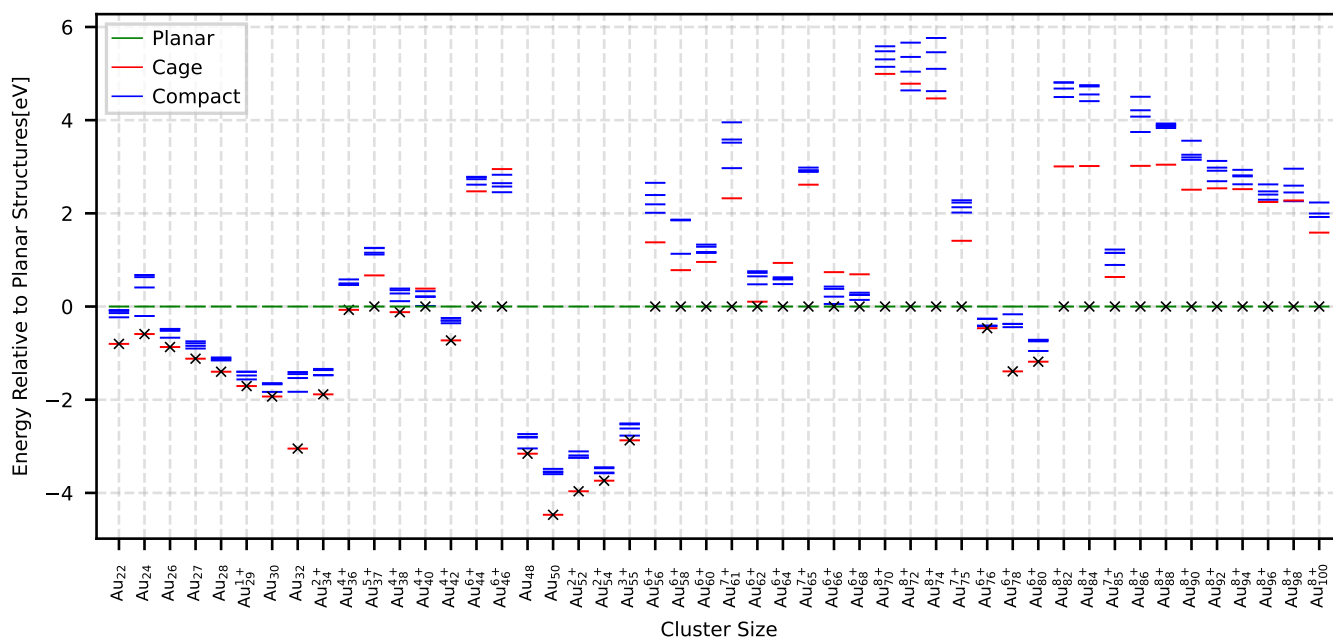


Fig. 1 Relative energies with respect to the planar structure for the smallest ionization level at which a cage or planar structure becomes the ground state within the PBE XC functional. The global minimum is marked by a cross sign.

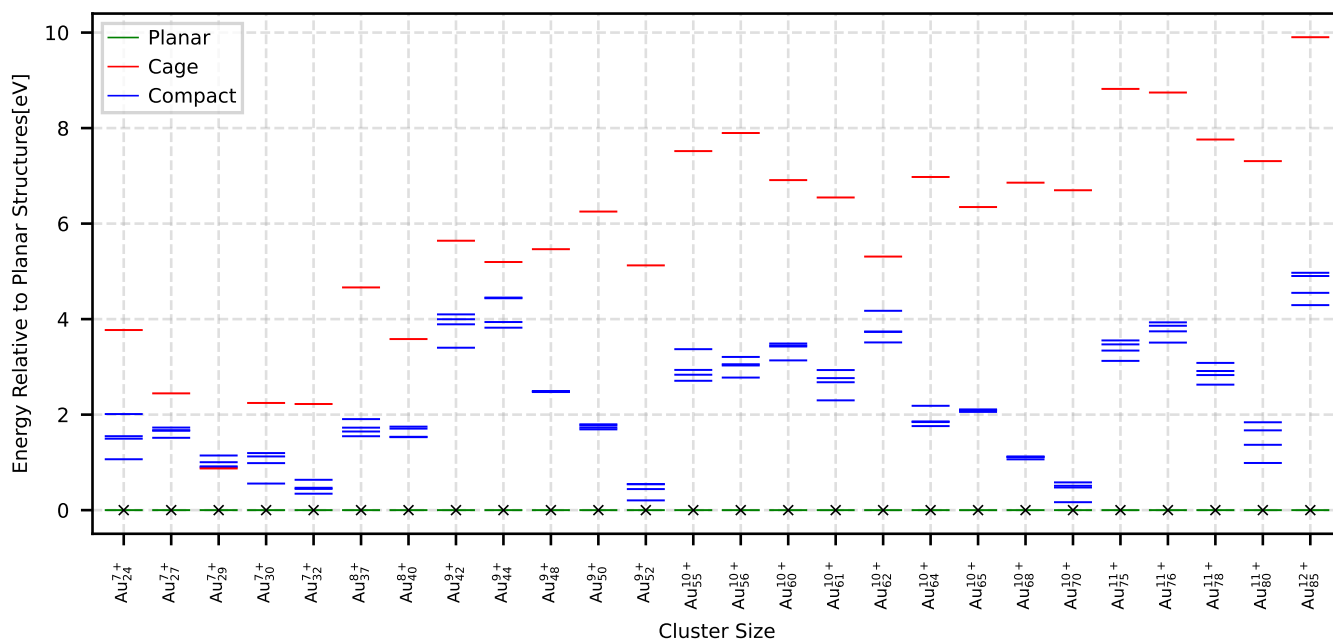


Fig. 2 Relative energies with respect to the planar structure for the smallest ionization level at which the planar structure becomes the ground state within the PBEsol+MBD XC functional. The global minimum, which is a planar structure for all cases, is marked by a cross sign.



and planar structures are shown in the Table SIII supplementary information.

3.3 r^2 SCAN

r^2 SCAN is a non-empirical, numerically regularized meta-GGA in the SCAN family that improves numerical stability while satisfying the most important known exact constraints for meta-GGA XC functionals. It builds on earlier regularization efforts r SCAN⁴⁵ that were introduced to mitigate SCAN's⁴⁶ numerical sensitivity, while SCAN itself was originally designed as a broadly constrained meta-GGA. Within the r^2 SCAN description, cage geometries are obtained as ground states for the neutral clusters Au_{24} , Au_{27} , and Au_{32} . Upon ionization, cages become the ground state for Au_{29}^{+1} , Au_{37}^{+5} , and Au_{55}^{+6} , whereas for all other investigated clusters, planar structures are stabilized as ground states at the corresponding ionization levels. Overall, the ionization level required to favor planar structures in r^2 SCAN lies between those predicted by PBE and by PBEsol+MBD, i.e., higher than in PBE but lower than in PBEsol+MBD. For planar ground states, the structural energy gaps are as follows: Au_{61}^{+8} , Au_{62}^{+8} , Au_{64}^{+8} , Au_{65}^{+8} and Au_{85}^{+9} fall between 2-3 eV; Au_{40}^{+6} , Au_{50}^{+7} , Au_{56}^{+7} , Au_{68}^{+8} and Au_{70}^{+8} fall between 1-2 eV; all remaining cases fall between 0-1 eV. In the table 1, the ionization levels required to stabilize non-compact motifs as ground states are listed. The resulting energetic ordering is shown in fig. 3. The total energy of the lowest energy compact, cage and planar structures are shown in the Table SIV supplementary information.

3.4 Density of states

The compact structures have a very high density of states, i.e., there exist many nearly degenerate structures. For each ionization level, we showed only the four lowest-energy compact structures. In general, there is a substantial structural energy gap between the planar global minimum and the lowest compact cluster as seen in figs. 1 to 3. So even if there was a slightly lower compact structure, it is very unlikely that it would be lower than the planar structures.

3.5 Temperature effects

We investigated the effects of temperature on the stability of planar structures by calculating the vibrational free energy at finite temperature. The results show that temperature effects further stabilize the planar geometries relative to their compact and cage counterparts. Figure 3 shows the free energies with respect to planar geometries. It can be seen that taking into account the temperature effects changes the global minimum of Au_{37} and Au_{55} from a cage to a planar configuration. In addition, the structural energy gap between planar geometries and the first metastable geometries get larger. The vibrational free energies for Au_{50} to Au_{85} are calculated by charge-corrected NequIP and for the rest by DFT using the r^2 SCAN XC functional at 300k.

3.6 Building patterns

To better understand the planar structural patterns, we analyzed their building patterns across multiple cluster sizes. The growth is not always achieved by completing full shells; in many cases, atoms are added selectively along edges or specific directions, leading to anisotropic yet regular structures as shown in fig. 4. For example, the transition from 55 to 85 atoms involves additions that extend particular edges rather than forming uniform shells. Even though the required minimum ionization level for obtaining planar structures varies for different XC functionals, the lowest energy planar structures of all XC functionals have the same overall structure. The different ionization levels and XC functionals just lead to barely visible structural relaxations.

3.7 Symmetries

In fig. 5 we highlight high-symmetry cage structures, Au_{32} (I_h), $Au_{27,29}$ (D_{3h}), Au_{37} (D_{5h}), $Au_{42,62}$ (D_{5d}), Au_{50} (D_{6d}) and Au_{78} (T_h). The assigned point-group symmetries, however, are XC functional dependent. For PBE and r^2 SCAN, these cages largely retain their high symmetry character; the only notable exception is Au_{27} , which relaxes from D_{3h} (PBE) to C_s (r^2 SCAN). With PBEsol+MBD, $Au_{32,37,42}$ clusters relax into strongly distorted cages and lose their symmetries. Intermediate symmetries are observed in: $Au_{22,24,26}$ (C_{2v}), Au_{28} (C_{3v}) and $Au_{34,75}$ (D_2). The rest of the cages, however, adopt low symmetry and are classified as C_s , C_2 and C_1 . Table 1 shows for the clusters that we calculated them with three XC functionals (with PBE XC functional we have calculated more clusters than the other two), the ionization level at which non-compact structures become energetically competitive, together with the point-group symmetry of the corresponding compact and cage at that ionization level for r^2 SCAN, PBEsol+MBD and PBE XC functionals. Taken together, these results demonstrate that while cage motifs frequently adopt highly symmetric forms, the compact structures favor distorted, low-symmetry configurations. Being trained on bulk materials, MACE gave only compact structures, but no low-energy cages. Finally, we note that the point-group symmetries reported here arise from the structures relaxed with a standard finite electronic smearing (Gaussian broadening) of 0.01 eV. In the zero-electronic-temperature limit, degenerate states at the Fermi level drive small Jahn-Teller distortions that lift the degeneracy by reducing the symmetry, and slightly lower the total energy. The distortions are, however, so small that they can hardly be seen by eye. In the resulting structures, all electronic levels are completely filled with integer occupation numbers, so the rule that determines the structure of small clusters, namely that clusters adopt shapes such that electronic shells can be filled completely⁴⁷, is also applicable to larger clusters.

4 Conclusions

In this study, we showed that ionization can transform the ground states of medium-sized clusters from compact bulk-like structures to planar structures consisting of hexagonal honeycomb patterns. These planar structures are considerably lower in energy than ionized compact structures of the same size. Weaker ionizations





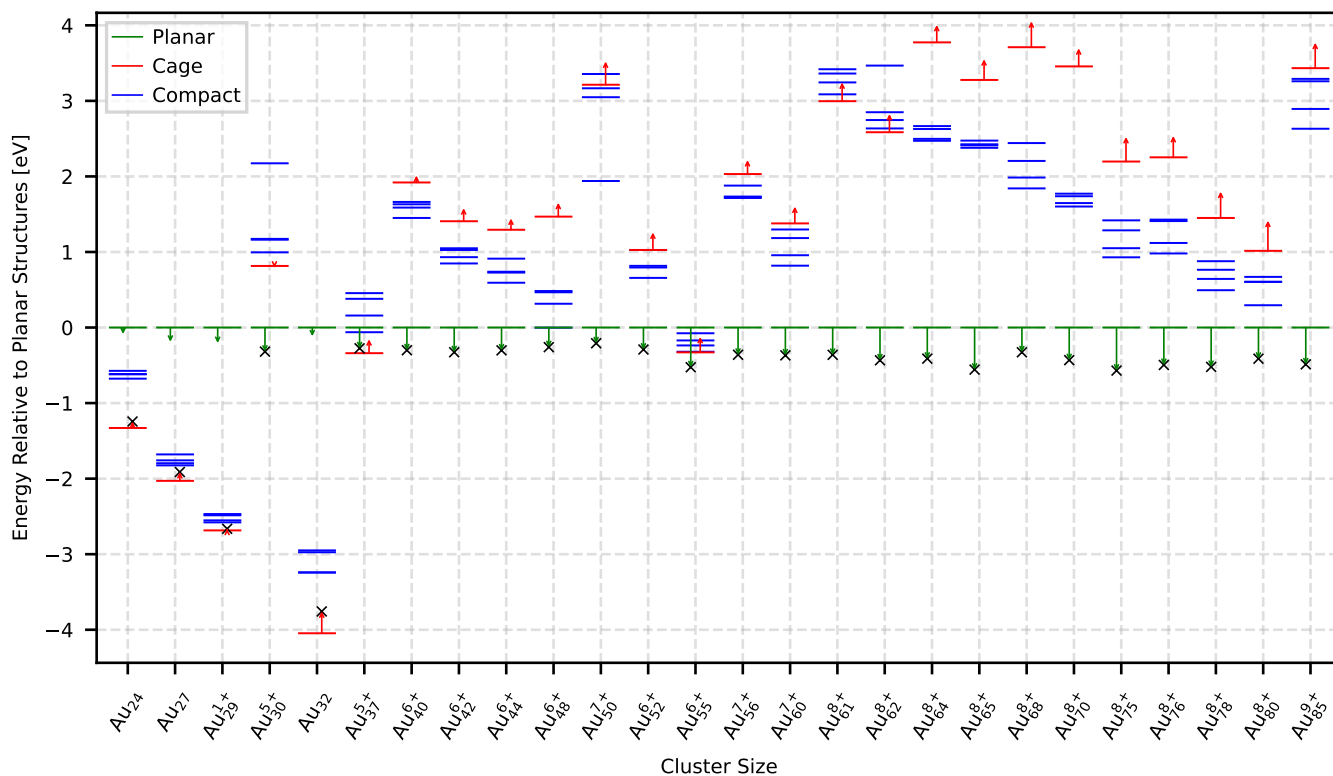


Fig. 3 Relative energies with respect to the planar structure for the smallest ionization level at which a cage or planar structure becomes the ground state within the r^2 SCAN XC functional. The plot also includes vibrational free energy contribution at 300 K, shown as arrows whose amplitudes represent the vibrational free energy differences relative to the vibrational free energy of the lowest-energy compact structure. A downward arrow indicates that inclusion of the vibrational free energy term stabilizes the corresponding structure, while an upward arrow indicates the opposite. The global minimum marked by a cross sign at the tip of the arrows.


Size: 22 → 28 → 38 → 88




Size: 24 → 42 → 44 → 70




Size: 26 → 72 → 74 → 98




Size: 27 → 34 → 50 → 86



Size: 29 → 60 → 68 → 76




Size: 30 → 52 → 78 → 80




Size: 32 → 46 → 82 → 92




Size: 36 → 37 → 61 → 62




Size: 40 → 48 → 56 → 64



Size: 54 → 84 → 90 → 96



Size: 55 → 65 → 75 → 85



Size: 58 → 66 → 94 → 100




Fig. 4 Planar configurations of minimally ionised gold clusters of all investigated sizes. The atoms are always arranged in a regular, close-packed hexagonal pattern. Progression from one size to the next is obtained by successively adding the atoms highlighted in red, then blue, and finally green, to the atoms shown in gold.



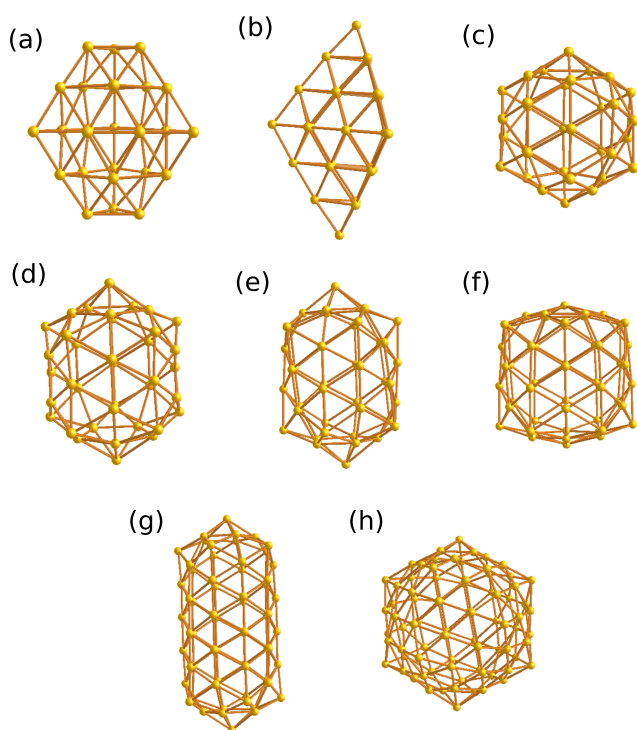


Fig. 5 Subfigure (a)-(h) show the highly symmetric cage structures for Au_{27} , Au_{29} , Au_{32} , Au_{37} , Au_{42} , Au_{50} , Au_{62} and Au_{78} respectively.

Table 1 For each cluster size, the table reports for the r^2 SCAN, PBEsol+MBD, and PBE XC functionals the ionization level Q at which the lowest-energy non-compact motif first becomes energetically competitive with the compact minimum, together with the point-group symmetry of the corresponding lowest-energy compact and cage structures at that Q .

Cluster	PBE		PBEsol+MBD			r^2 SCAN			
	Q	compact	cage	Q	compact	cage	Q	compact	cage
Au_{24}	0	C_s	C_{2v}	8	C_{2v}	C_{2v}	0	C_1	C_{2v}
Au_{27}	0	C_{2v}	D_{3h}	7	C_s	D_{3h}	0	C_s	C_s
Au_{29}	1	C_{3v}	D_{3h}	7	C_s	D_{3h}	1	C_1	D_{3h}
Au_{30}	0	C_1	C_1	7	C_s	C_1	5	C_1	C_1
Au_{32}	0	C_1	I_h	7	C_3	C_1	0	C_s	I_h
Au_{37}	5	C_1	D_{5h}	8	C_1	C_2	5	C_s	D_{5h}
Au_{40}	4	C_1	C_1	8	C_1	C_1	6	C_1	C_s
Au_{42}	4	C_1	D_{5d}	9	C_1	C_1	6	C_1	D_{5d}
Au_{44}	6	C_s	C_1	9	C_1	C_1	6	C_s	C_1
Au_{48}	0	C_s	C_2	9	C_s	C_1	6	C_s	C_2
Au_{50}	0	C_1	D_{6d}	9	C_1	D_{6d}	7	C_3	D_{6d}
Au_{52}	2	C_1	C_1	9	C_{2v}	C_1	6	C_1	C_1
Au_{55}	3	C_1	C_1	10	C_s	C_1	6	C_1	C_1
Au_{56}	6	C_1	C_1	10	C_1	C_1	7	C_1	C_1
Au_{60}	6	C_2	C_2	10	C_1	C_2	7	C_1	C_2
Au_{61}	7	C_3	C_1	10	C_1	C_1	8	C_1	C_1
Au_{62}	6	C_3	D_{5d}	10	C_3	D_{5d}	8	C_3	D_{5d}
Au_{64}	6	C_2	C_1	10	C_1	C_1	8	C_1	C_1
Au_{65}	7	C_1	C_1	10	C_1	C_1	8	C_1	C_1
Au_{68}	6	C_1	C_1	10	C_2	C_1	8	D_2	C_1
Au_{70}	8	C_1	C_1	10	C_1	C_1	8	C_1	C_1
Au_{75}	7	C_2	C_2	11	C_1	D_2	8	C_2	C_2
Au_{76}	6	C_1	C_1	11	C_1	C_1	8	C_1	C_1
Au_{78}	6	C_1	T_h	11	C_1	T_h	8	C_1	T_h
Au_{80}	6	C_1	C_1	11	C_1	C_2	8	C_1	C_2
Au_{85}	7	C_1	C_1	12	C_1	C_1	9	C_1	C_1

can also lead to cage structures. The predicted degree of ionization that is necessary to induce cage or planar ground states, unfortunately, depends on the XC functional that is used. We found that the PBE XC functional requires the smallest amount of ionization to induce planar ground states. The r^2 SCAN requires a somewhat larger ionization and PBEsol+MBD requires the largest amount. The r^2 SCAN XC functional, which also includes dispersion interactions, would probably be considered by most researchers as the most accurate XC functional. It yields results in closest agreement with experiment. PBEsol+MBD predicts compact ground states for all neutral clusters. For some sizes such as Au_{24} , Au_{27} and Au_{32} there are however experimental indications that the ground states are cages^{14,16,48}. This is also predicted by the PBE and r^2 SCAN XC functionals. In contrast to experimental evidence, cages are never lower in energy than planar structures with the PBEsol+MBD XC functional. So we also consider in this context the r^2 SCAN results as the most reliable results. The ionization level given in table 1 should therefore best match an experimental verification of our results. Although the minimum ionization level at which planar or cage structures become the global minima depends on the XC functional, the overall conclusion remains unchanged: ionization stabilizes non-compact structures across all functionals considered.

Conflicts of interest

There are no conflicts to declare.

Data availability

The coordinate files for all structures reported in this paper are deposited and are provided in the accompanying zipped archive. Further information regarding the data can be obtained by contacting the corresponding author via email.

Acknowledgements

Computational resources were provided by the Swiss National Supercomputing Centre (CSCS) under projects s1167 and lp08, and by sciCORE, the scientific computing center of the University of Basel. Financial support for this project was provided by SNF under grant number 200021_191994. M.I.S thanks and appreciates the interesting discussions with M. Gubler, M. Sommer-Jørgensen and G. Fiscaro.

Notes and references

- 1 F. Furche, R. Ahlrichs, P. Weis, C. R. Jacob, S. Gilb, T. Bierweiler and M. M. Kappes, *J. Chem. Phys.*, 2002, **117**, 6982–6990.
- 2 H. Häkkinen and U. Landman, *Phys. Rev. B*, 2000, **62**, R2287–R2290.
- 3 H. Häkkinen, B. Yoon, U. Landman, X. Li, H.-J. Zhai and L.-S. Wang, *J. Phys. Chem. A*, 2003, **107**, 6168–6175.
- 4 J. Wang, G. Wang and J. Zhao, *Phys. Rev. B*, 2002, **66**, 035418.
- 5 X. Xing, B. Yoon, U. Landman and J. H. Parks, *Phys. Rev. B*, 2006, **74**, 165423.
- 6 R. Pal, L.-M. Wang, W. Huang, L.-S. Wang and X. C. Zeng, *J. Chem. Phys.*, 2011, **134**, 054306.



- 7 E. M. Fernández, J. M. Soler and L. C. Balbás, *Phys. Rev. B*, 2006, **73**, 235433.
- 8 B. R. Goldsmith, J. Florian, J.-X. Liu, P. Gruene, J. T. Lyon, D. M. Rayner, A. Fielicke, M. Scheffler and L. M. Ghiringhelli, *Phys. Rev. Materials*, 2019, **3**, 016002.
- 9 L. P. Ding, H. Liu, H. Y. Xu, S. F. Lei, P. Shao and F. Ding, *Mater. Today Nano*, 2025, **30**, 100634.
- 10 S. Bulusu, X. Li, L.-S. Wang and X. C. Zeng, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 8326–8330.
- 11 J. Li, X. Li, H.-J. Zhai and L.-S. Wang, *Science*, 2003, **299**, 864–867.
- 12 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 13 B. Schaefer, R. Pal, N. S. Khetrpal, M. Amsler, A. Sadeghi, V. Blum, X. C. Zeng, S. Goedecker and L.-S. Wang, *ACS Nano*, 2014, **8**, 7413–7422.
- 14 P. V. Nhat, N. T. Si, V. G. Kiselev and M. T. Nguyen, *J. Comput. Chem.*, 2021, **42**, 2145–2153.
- 15 A. Hirsch, Z. Chen and H. Jiao, *Angew. Chem. Int. Ed.*, 2000, **39**, 3915–3917.
- 16 M. Ji, X. Gu, X. Li, X. Gong, J. Li and L.-S. Wang, *Angew. Chem. Int. Ed.*, 2005, **44**, 7119–7123.
- 17 D. Tian, J. Zhao, B. Wang and R. B. King, *J. Phys. Chem. A*, 2007, **111**, 411–414.
- 18 J. Wang, J. Jellinek, J. Zhao, Z. Chen, R. B. King and P. von Ragué Schleyer, *J. Phys. Chem. A*, 2005, **109**, 9265–9269.
- 19 Y. Gao and X. C. Zeng, *J. Am. Chem. Soc.*, 2005, **127**, 3698–3699.
- 20 S. M. Mullins, R. L. Whetten, H.-C. Weissker and X. López-Lozano, *J. Chem. Phys.*, 2021, **155**, 204307.
- 21 H. Ning, J. Wang, Q.-M. Ma, H.-Y. Han and Y. Liu, *J. Phys. Chem. Solids*, 2014, **75**, 696–699.
- 22 K. Bao, S. Goedecker, K. Koga, F. Lançon and A. Neelov, *Phys. Rev. B*, 2009, **79**, 041405.
- 23 L. Song, Y. Huang, Z. Nie and T. Chen, *Nanoscale*, 2020, **12**, 7433–7460.
- 24 S. Forti, S. Link, A. Stöhr, Y. Niu, A. A. Zakharov, C. Coletti and U. Starke, *Nat. Commun.*, 2020, **11**, 2236.
- 25 S. Kashiwaya, Y. Shi, J. Lu, D. G. Sangiovanni, G. Greczynski, M. Magnuson, M. Andersson, J. Rosen and L. Hultman, *Nat. Synth.*, 2024, **3**, 744–751.
- 26 X. Wang, C. Wang, C. Chen, H. Duan and K. Du, *Nano Lett.*, 2019, **19**, 4560–4566.
- 27 L. Zhao, H. Q. Ta, R. G. Mendes, A. Bachmatiuk and M. H. Rummeli, *Adv. Mater. Interfaces*, 2020, **7**, 2000436.
- 28 S. Ono, *Phys. Rev. B*, 2020, **102**, 165424.
- 29 L.-M. Yang, M. Dornfeld, T. Frauenheim and E. Ganz, *Phys. Chem. Chem. Phys.*, 2015, **17**, 26036–26042.
- 30 J. Nevalaita and P. Koskinen, *Nanoscale*, 2019, **11**, 22019–22024.
- 31 P. Koskinen and T. Korhonen, *Nanoscale*, 2015, **7**, 10140–10145.
- 32 S. Ye, A. P. Brown, A. C. Stammers, N. H. Thomson, J. Wen, L. Roach, R. J. Bushby, P. L. Coletta, K. Critchley, S. D. Connell, A. F. Markham, R. Brydson and S. D. Evans, *Adv. Sci.*, 2019, **6**, 1900911.
- 33 V. S. Marangoni, L. D. Germano, C. C. C. Silva, E. A. de Souza and C. M. Maroneze, *Nanoscale*, 2018, **10**, 13315–13319.
- 34 L. Wang, Y. Zhu, J.-Q. Wang, F. Liu, J. Huang, X. Meng, J.-M. Basset, Y. Han and F.-S. Xiao, *Nat. Commun.*, 2015, **6**, 6957.
- 35 S. Goedecker, *J. Chem. Phys.*, 2004, **120**, 9911–9917.
- 36 M. Krummenacher, M. Gubler, J. A. Finkler, H. Huber, M. Sommer-Jørgensen and S. Goedecker, *SoftwareX*, 2024, **25**, 101632.
- 37 H. Huber, M. Sommer-Jørgensen, M. Gubler and S. Goedecker, *Phys. Rev. Res.*, 2023, **5**, 013189.
- 38 S. Batzner, A. Musaelian, L. Sun, M. Geiger, J. P. Mailoa, M. Kornbluth, N. Molinari, T. E. Smidt and B. Kozinsky, *Nat. Commun.*, 2022, **13**, 2453.
- 39 I. Batatia, P. Benner, Y. Chiang, A. M. Elena, D. P. Kovács, J. Riebesell, X. R. Advincula, M. Asta, W. J. Baldwin, N. Bernstein, A. Bhowmik, S. M. Blau, V. Cărare, J. P. Darby, S. De, F. D. Pia, V. L. Deringer, R. Elijošius, Z. El-Machachi, E. Fako, A. C. Ferrari, A. Genreith-Schriever, J. George, R. E. A. Goodall, C. P. Grey, S. Han, W. Handley, H. H. Heenen, K. Hermansson, C. Holm, J. Jaafar, S. Hofmann, K. S. Jakob, H. Jung, V. Kapil, A. D. Kaplan, N. Karimitari, N. Kroupa, J. Kullgren, M. C. Kuner, D. Kuryla, G. Liepuoniute, J. T. Margraf, I.-B. Magdău, A. Michaelides, J. H. Moore, A. A. Naik, S. P. Niblett, S. W. Norwood, N. O'Neill, C. Ortner, K. A. Persson, K. Reuter, A. S. Rosen, L. L. Schaaf, C. Schran, E. Sivonxay, T. K. Stenczel, V. Svahn, C. Sutton, C. van der Oord, E. Varga-Umbrich, T. Vegge, M. Vondrák, Y. Wang, W. C. Witt, F. Zills and G. Csányi, *J. Chem. Phys.*, 2025, **163**, 184110.
- 40 V. Blum, R. Gehrke, F. Hanke, P. Havu, V. Havu, X. Ren, K. Reuter and M. Scheffler, *Comput. Phys. Commun.*, 2009, **180**, 2175–2196.
- 41 E. van Lenthe, E. J. Baerends and J. G. Snijders, *J. Chem. Phys.*, 1993, **99**, 4597–4610.
- 42 J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou and K. Burke, *Phys. Rev. Lett.*, 2008, **100**, 136406.
- 43 A. Tkatchenko, J. DiStasio, Robert A., R. Car and M. Scheffler, *Phys. Rev. Lett.*, 2012, **108**, 236402.
- 44 J. W. Furness, A. D. Kaplan, J. Ning, J. P. Perdew and J. Sun, *J. Phys. Chem. Lett.*, 2020, **11**, 8208–8215.
- 45 A. P. Bartók and J. R. Yates, *J. Chem. Phys.*, 2019, **150**, 161101.
- 46 J. Sun, A. Ruzsinszky and J. P. Perdew, *Phys. Rev. Lett.*, 2015, **115**, 036402.
- 47 G. Fisticaro, B. Schaefer, J. A. Finkler and S. Goedecker, *Mater. Adv.*, 2023, **4**, 1746–1768.
- 48 B. Yoon, P. Koskinen, B. Huber, O. Kostko, B. von Issendorff, H. Häkkinen, M. Moseler and U. Landman, *ChemPhysChem*, 2007, **8**, 157–161.



The coordinate files for all structures reported in this paper are deposited and are provided in the accompanying zipped archive. Further information regarding the data can be obtained by contacting the corresponding author via email.

[View Article Online](#)
DOI: 10.1039/D6NA00102E

Open Access Article. Published on 22 May 2026. Downloaded on 5/23/2026 10:24:43 AM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

