


 Cite this: *RSC Adv.*, 2026, 16, 13252

Recent progress in the fabrication of nanocomposite-derived superhydrophobic coatings for improved concrete lifespan: insights into recent advancements, interfacial chemistry and tribological performance

 Sahita Karmakar,^a Pranav R. T. Peddinti,^b Young-Nam Kwon^c and Saikat Sinha Ray *^a

Concrete structures and built infrastructure are essential for modern civilization due to the increasing urbanization, population growth, and corresponding infrastructure needs. However, extreme weather and prolonged exposure to humidity can lead to the irreversible degradation of various materials used in built infrastructure, primarily due to water penetration and freeze–thaw cycles. This review examines the effectiveness and successful application of protective surface coatings on concrete, a major construction material. Superhydrophobic coatings meet the demands of various applications, offering anti-microbial resistance, corrosion resistance, contamination prevention, water repellence, drag reduction, anti-icing, anti-fogging, anti-adhesion features, and self-cleaning capabilities. Nanocomposites are known for their improved mechanical, thermomechanical, and thermal properties compared with their base materials, drawing considerable interest from researchers worldwide. The key problem of insufficient mechanical and chemical durability of superhydrophobic materials when applied on concrete surfaces is pointed out, and the application trend of these materials is projected. In addition, the tribology discussed in this review primarily addresses their mechanical durability, wear resistance, and long-term performance. This review also covers recent advancements in fabrication techniques, current limitations, and testing methods for superhydrophobic concrete. The effects of hydrophobic treatments on the hydration process, which is crucial for the development of compressive strength in concrete, are explored. Furthermore, successful case studies of superhydrophobic coatings for protecting concrete structures are presented. To develop maintenance strategies, prevent failures, and adhere to industrial standards, it is vital to assess the durability and characteristics of these coatings while considering factors such as mechanical stress, environmental exposure, and other qualitative aspects. The overall findings from this review could facilitate enhancing the advancement of durable, efficient concrete materials.

 Received 9th December 2025
 Accepted 18th February 2026

DOI: 10.1039/d5ra09515h

rsc.li/rsc-advances

1 Introduction

Concrete structures and building materials intrinsically impact the daily lives and safety of residents, significantly influencing urban growth and the reputation of construction enterprises. Urban infrastructures suffer from considerable damages due to pollution from dust, organic pollutants in the air, and microbes, which degrade concrete structures and create aesthetic deterioration.¹ Water seepage in concrete structures has caused significant challenges and disruptions for societies globally. Waterproofing issues are recognized as the primary cause of structural failures, leading to moisture problems.²

Recently, the coating industry has gained significant attention. Super-hydrophobic coatings are employed in the building sector because of their remarkable qualities, offering various functional benefits such as anti-microbial resistance, anti-fogging, anti-corrosion, anti-fouling, self-cleaning, and drag reduction capabilities. Furthermore, customizing the properties of these coatings to meet important performance standards, such as transparency, UV resistance, anti-reflection, anti-water penetration, and thermal insulation, using various fabrication technologies and materials has enhanced their applications across diverse fields.³

^aDepartment of Environmental Science and Engineering, SRM University-AP, Amaravati, Andhra Pradesh 522240, India. E-mail: ssinharay6@gmail.com

^bDepartment of Civil Engineering, SRM University-AP, Amaravati, Andhra Pradesh 522240, India

^cDepartment of Civil, Urban, Earth, and Environmental Engineering, Ulsan National Institute of Science and Technology (UNIST), Ulsan 44919, Republic of Korea



Fig. 1 represents the country-wise research productivity related to the conservation of heritage structures, as identified from the literature. Fig. 1(a) shows the distribution of global research outputs from different countries that have more than a thousand publications related to conservation of heritage sites. It visualizes the top countries involved in research and development worldwide in conserving their heritage based on a comprehensive dataset collected from an advanced search in Scopus. The United States, China, Italy, and United Kingdom

stand out as global leaders, exhibiting the highest levels of heritage conservation activity.

The methodology for conducting the comprehensive literature review on nanocomposite-based superhydrophobic coatings is shown in Fig. 2 using bibliometric analysis.^{4,5} Step 1 defines the research intention and objectives. In step 2, a set of relevant keywords is identified. In step 3, the identified keywords are used in different combinations that can help to find the required literature, for example, 'Nanocomposite' OR 'Superhydrophobic' AND 'Heritage' OR 'Conservation'. Then, the literature search is conducted, and the dataset is



Sahita Karmakar

Ms Sahita Karmakar, a second-year PhD scholar at SRM University, Andhra Pradesh, is working on nanocomposite-based materials, under Dr Saikat Sinha Ray. She completed her Bachelor's degree in Zoology in 2019 and Master's degree in Environmental Science in 2021 from the University of Calcutta. Following her postgraduation, she completed a one-year internship (2022–2023) at the Zoological Survey of India,

focusing on the identification of Hymenoptera: Formicidae, and a six-month internship at the South Asian Forum for Environment (SAFE NGO). She has presented papers at several international and national level conferences. She has published four review papers in peer reviewed journals and four book chapters in reputed platforms of Springer Nature, Elsevier, the Zoological Survey of India, and others.



Pranav R. T. Peddinti

Dr Pranav R. T. Peddinti is an Assistant Professor in the Department of Civil Engineering and a Coordinator of the Centre for Drone Technology at SRM University AP, India. Dr Peddinti is a Civil engineering professional, specializing in pavement geotechnics, UAV-based infrastructure monitoring, and sustainable materials. He obtained a PhD in Pavement Geotechnics from IIT Hyderabad while working on system

reliability-based pavement designs. His Research Professorship as a Brain Pool Fellow at UNIST, South Korea, focused on developing innovative drone technology applications in infrastructure condition assessment and non-destructive testing. Dr Peddinti has also authored multiple research papers, published in several journals.



Young-Nam Kwon

Dr Young-Nam Kwon is a Professor in the Department of Civil, Urban, Earth, and Environmental Engineering at the Ulsan National Institute of Science and Technology (UNIST), South Korea. He earned his PhD in Civil and Environmental Engineering from Stanford University and has served as a Postdoctoral Scholar in the same institution. His research focuses on the core areas of the Superior Membrane-

based Advanced Research & Technology (SMART) Lab, including membrane technology for water treatment, seawater desalination, and the development of innovative self-cleaning and superhydrophobic surfaces. Dr Kwon has authored numerous research papers in leading journals and holds several patents in the fields of membrane fabrication, CO₂ separation, and advanced water purification technologies.




Saikat Sinha Ray


Dr Saikat Sinha Ray is an Assistant Professor in the Department of Environmental Science and Engineering at SRM University-AP, Andhra Pradesh, India. He earned his PhD from the National Taipei University of Technology, Taiwan, and has served as a Research Assistant Professor in the Department of Urban and Environmental Engineering at Ulsan National Institute of Science and Technology (UNIST), South Korea. His

research interests include membrane fabrication, seawater desalination, membrane distillation, self-cleaning surfaces, and superhydrophobic surfaces for various environmental applications. He has published multiple research papers and review articles in several leading journals.



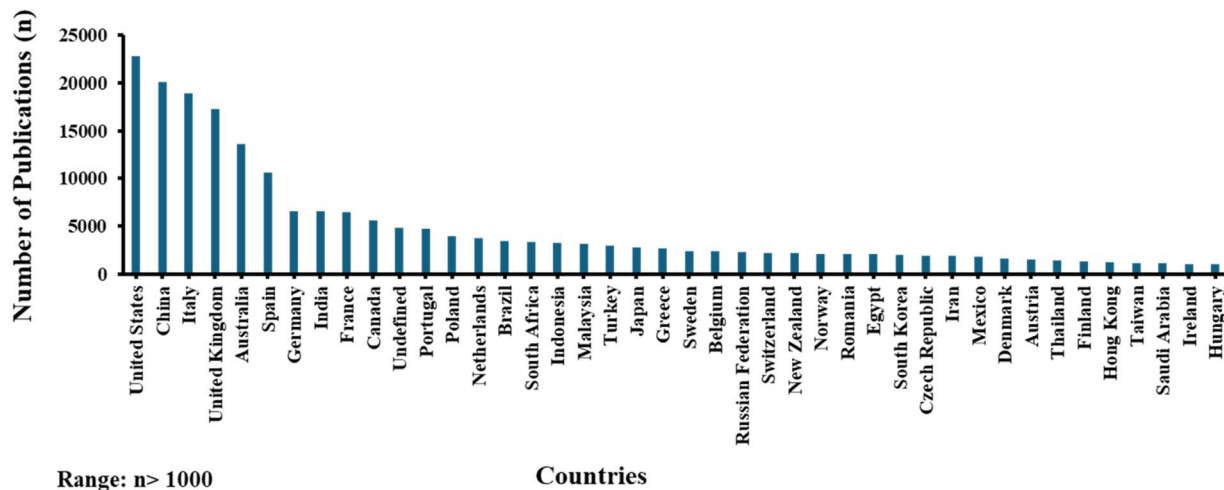

(a)

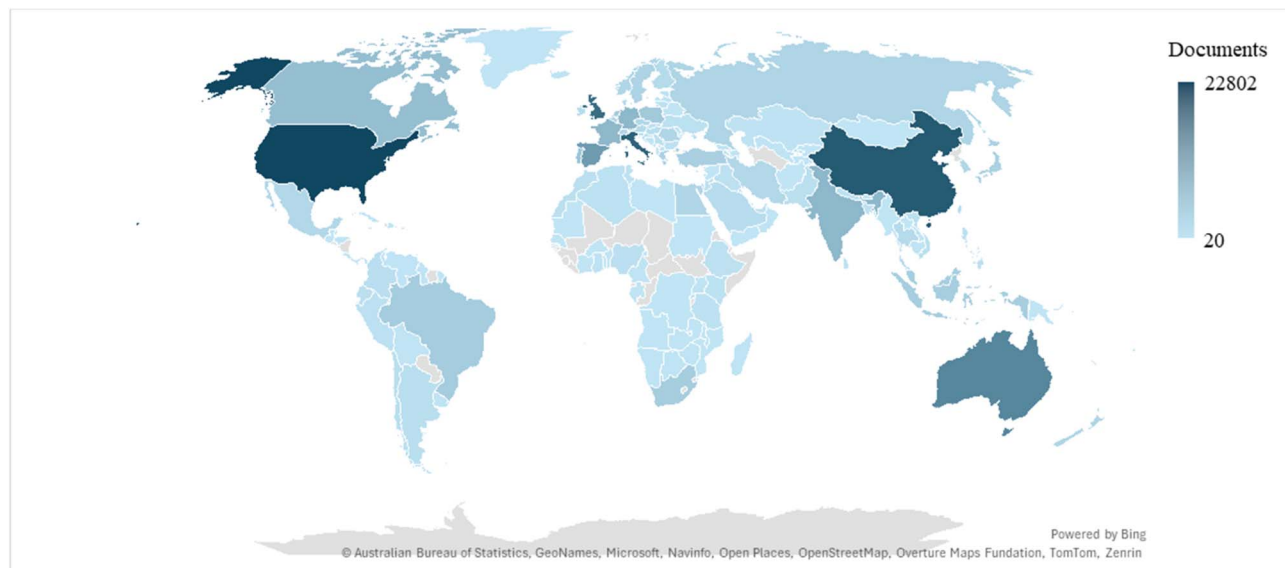

(b)

Fig. 1 Global geographical distribution of scientific publications in conserving their heritage. The database was collected from an advanced search in Scopus using the terms "conservation" and "heritage" from 2005 to 2025 as of February 2026.

downloaded. This phase collects peer-reviewed publications from established databases, such as Scopus, Web of Science, ScienceDirect, and ResearchGate, to build a custom dataset that captures a broad range of relevant publications. Regarding the databases, only those that provide a larger number of works on the research topic were selected. Step 4 usually includes a final database search using Zotero Reference Manager. In step 5, the articles are analysed individually, excluding titles unrelated to

the area. Typically, a temporal limit is imposed to customise the literature review in step 6. Determining whether the full paper is available for download is the next step. The final phase includes reading and systematic analysis of the papers collected thereafter. This can be one of the fundamental approaches of bibliometric analysis in this research area.

Typically, there are two main approaches for achieving superhydrophobicity in concrete, namely, surface coating and



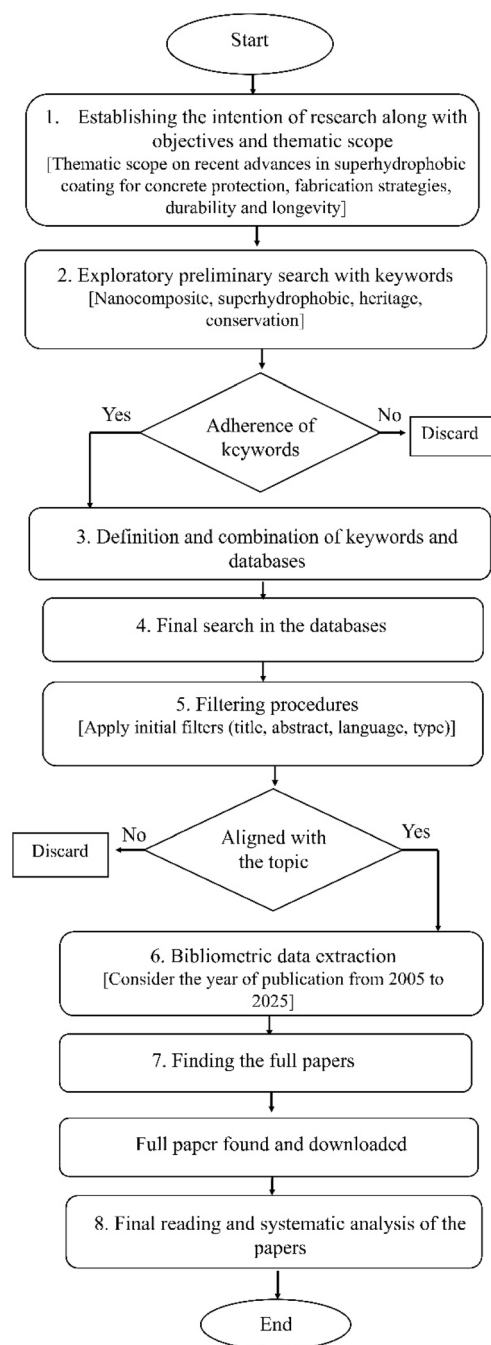


Fig. 2 Bibliometric analysis of the methodology for the literature search strategy.

integrated modification; however, they face distinct challenges in maintaining a balance between the robustness and mechanical strength of the resulting concrete.⁵ Superhydrophobic coatings, which rely on low surface energy micro- and nano-scale structures, are particularly vulnerable to structural degradation under localized load accumulation, leading to the collapse of trapped air cushions at the solid-liquid interface.⁷ When this protective surface structure is compromised by mechanical wear, chemical corrosion, or environmental aging, it exposes the underlying hydrophilic concrete substrate.

Superhydrophobic coatings show significant potential for heritage protection because of their excellent wetting resistance. As emerging technology, these coatings can help safeguard artifacts from damage caused by acid rain and precipitation. Their low surface energy and roughness further enhance their wetting resistance. Chemical materials such as silicones and fluoropolymers are commonly used to achieve low surface energy.⁸

Fig. 3 illustrates the country-wise distribution of research productivity related to superhydrophobic nanocoating materials for building protection. A survey has been conducted on peer reviewed publications since 2005 from different countries, demonstrating the growing interest in research articles on the superhydrophobic modification of nano-based materials. As shown in Fig. 3, China leads significantly with the highest number of publications, highlighting its strong research focus in this domain. Other countries, such as India, the United States, Iran, South Korea, and the United Kingdom, also exhibit moderate research activity in building conservation and related construction-material applications. This emerging interdisciplinary field addresses the growing need for innovative materials to combat structural degradation due to environmental and chemical exposure. Numerous researchers have systematically explored superhydrophobic nano-based materials from various angles, including surface or matrix hydrophobic modification, performance evaluation, mechanism analysis, development of hydrophobic agents, and engineering applications.

Composite and nanocomposite materials are made from different matrices, such as polymers, carbon, metals, and ceramics, combined with reinforcements such as particles, fibers, and layered materials.⁹ Compared to traditional polymer composites, polymer nanocomposites exhibit enhanced mechanical and tensile strength, superior scratch resistance, a higher heat distortion temperature, and effective noise reduction.¹⁰ Common challenges associated with high reinforcement levels in composites, such as lower toughness, decreased optical clarity, and increased melt viscosity, are minimized in nanocomposite production, as a nano-reinforcement loading of less than 10 wt% is sufficient for creating high-performance polymer nanocomposites.¹¹ The longevity of nanocomposite-based protective coatings is crucial for decreasing maintenance expenses and maximizing the service life of structures.

These coatings are subjected to mechanical stresses, such as abrasion and impact, which exacerbate wear. Therefore, reliable inspection techniques are required to monitor the performance of coatings throughout their lifetimes.¹² Historically, evaluations of coatings have predominantly relied on visual inspections and invasive testing techniques, including cross-cut adhesion assessments and pull-off strength measurements (Ovie *et al.*, 2024).¹³ These techniques provide direct and quantifiable results; they often require localized sampling, which can compromise structural integrity.¹⁴

Currently, research focuses on the superhydrophobic modification of nano-based materials aimed at preserving concrete structures and heritage sites. However, there is a significant lack of standardized and affordable superhydrophobic coatings that



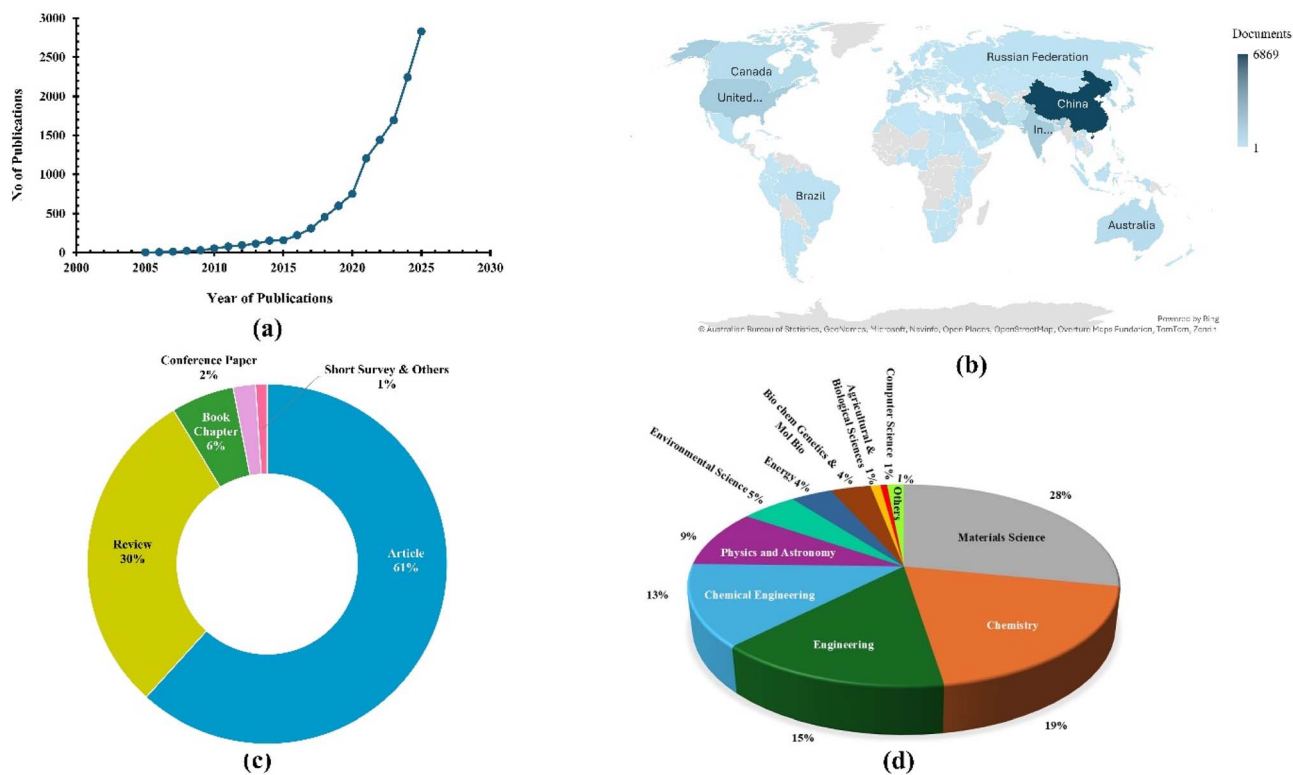


Fig. 3 (a) Survey on the number of research papers published year-wise since 2005. (b) Number of documents published from different countries. (c) Different categories of publications. (d) Contributions from different subject areas. These databases were collected from an advanced search in Scopus with the terms "superhydrophobic" and "nanocomposite for building" as of February 2026.

guarantee durability.¹⁵ Fig. 4 illustrates the properties and effects of a surface treatment by comparing treated and untreated surfaces. The untreated surface is smooth, allowing

liquids (*e.g.*, rainwater) to spread, resulting in lower contact angles and higher surface energy. In contrast, the treated surface exhibits a lower surface energy and higher contact

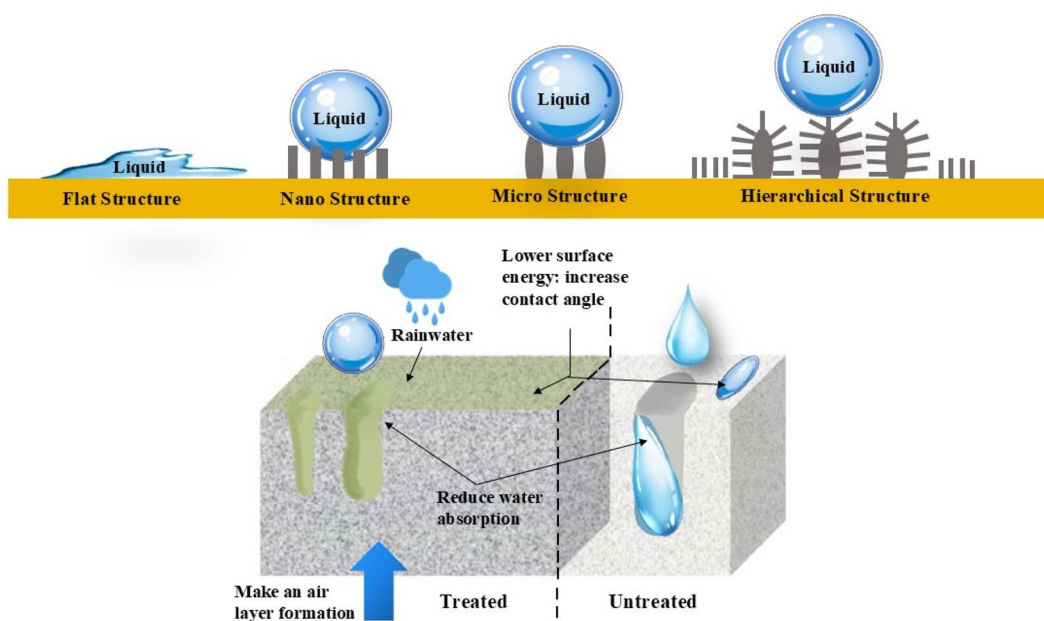


Fig. 4 Self-cleaning behavior of surfaces treated with and without nanocomposite-based superhydrophobic coating materials.



angles, which enable it to repel water. Additionally, this surface features nano- or micro-scale roughness, which traps air and decreases the interaction between the liquid and solid.^{16,17} These coatings are designed to provide excellent water repellency, self-cleaning properties, and resistance to environmental degradation by utilizing affordable nanomaterials and scalable production techniques, making them suitable for a broader range of applications.¹⁸ This approach not only extends the lifespan of valuable architectural and cultural assets but also promotes environmentally conscious preservation by reducing maintenance needs and reliance on harmful chemicals.¹⁹

This review concentrates on the effectiveness and synthesis of superhydrophobic nanocomposite-based coating materials for preserving concrete structures while discussing the classification and synthesis processes of these coatings. Their fabrication techniques and durability tests are enhanced to assess their water repellency capabilities. It also discusses the tribology performance and durability of nano-composite-based superhydrophobic coatings under mechanical stress due to their micro/nano-structured surfaces, which enable extremely low wettability and improved resistance to friction, wear, and deformation. These coatings maintain their water-repellent properties, reduce friction coefficients, and minimize material loss even under repeated abrasion, making them ideally suited for long-term applications.

Furthermore, this review addresses sustainability challenges, focusing on eco-friendly materials and scalable production methods, and provides techno-economic analyses to assess the cost-effectiveness of these approaches for large-scale applications. Despite the significant advancements in the fabrication of nanocomposite-derived superhydrophobic coatings for enhancing the lifespan of concrete, several research gaps persist, particularly in areas of long-term durability, real-world applicability, and interfacial chemistry. One major gap is the limited understanding of their long-term mechanical and chemical stability under harsh environmental conditions. Additionally, gaps remain in field testing and scalability for practical applications, with many formulations showing promise in laboratory settings but lacking data on real-world performance. Ultimately, a research gap remains regarding the techno-economic factors of nanomaterial-based techniques, which tend to be expensive. Therefore, future research must emphasize improving both durability and cost-effectiveness.

2 Fundamentals of superhydrophobicity for concrete coatings

Inspired by the “lotus effect,” superhydrophobic surfaces effectively repel water. Specifically, low-adhesion superhydrophobic surfaces with a high-water contact angle and reduced contact angle hysteresis enhance the self-removal of liquid and particulate contaminants.^{20,21} Their unique properties make them ideal for applications including anti-fogging, self-cleaning, anti-icing, heat transfer enhancement, and energy harvesting. Recent developments in coating technologies, especially the advent of

smart superhydrophobic coatings, have made these materials multifunctional and highly efficient, attracting considerable interest among researchers globally.⁷ Furthermore, these innovations have expanded the potential applications of superhydrophobic coatings by improving essential performance traits through various fabrication techniques and materials. Key characteristics include transparency, UV resistance, anti-reflective features, water penetration resistance, thermal insulation, and flame retardancy.²²

2.1 Surface properties governing superhydrophobicity

A superhydrophobic surface has a high-water contact angle (WCA) exceeding 150° and a low contact angle hysteresis (CAH) or sliding angle (SA) below 10° . Fig. 5 depicts that the wetting characteristics of these surfaces can be described using the theoretical models proposed by Young, Wenzel, and Cassie–Baxter.²³ The Young model represents thermodynamic equilibrium among solid, liquid, and vapor phases on an ideal, smooth, and uniform solid surface. In the Cassie–Baxter model, for example, a droplet rests on the tips of surface protrusions, with air pockets trapped beneath. In contrast, the classical Wenzel model depicts liquid droplets contacting every point on the underlying solid surface.²⁴ The wettability of materials is determined by their surface-free energy and surface roughness, which can be explained through the principle of surface hydrophobicity. Wettability refers to the ease with which a surface absorbs or repels water.²⁵ On surfaces with low wettability, water cannot infiltrate, which can prevent structural damage, staining, or the growth of mold and algae. High contact angle surfaces (greater than 150° , typical for superhydrophobic surfaces) demonstrate excellent water repellency, preventing moisture ingress, freeze–thaw cycles, and the accumulation of pollutants.²² Surface roughness is crucial in preserving construction and heritage materials, directly affecting their interaction with water and contaminants. The roughness is significantly enhanced by creating micro- or nano-scale textures, which improve the hydrophobic or superhydrophobic properties, allowing water beads to roll off rather than penetrate the surface.²⁶

2.2 Technological and engineering applications of superhydrophobic coatings

Superhydrophobic surfaces achieve their protective properties through tailored surface chemistry, hierarchical micro/nanoscale roughness, and advanced material engineering. These mechanisms work synergistically to repel water, resist corrosion, enable self-cleaning, and withstand UV degradation.²⁷ The extent to which a solid can repel a liquid relies on two key factors, its surface energy and surface morphology. A reduction in surface energy enhances its hydrophobicity. The chemical composition of a surface determines its surface energy, which in turn strongly affects its wettability. In a superhydrophobic surface, its surface morphology plays a crucial role in determining its wettability.²⁸ Roughening a surface can intensify its hydrophobicity not only because of the increased solid–liquid interface but also because air can be trapped between the rough surface and a liquid droplet. Since the air layer acts as a hydrophobic material with a contact angle



Table 1 Overview of the superhydrophobic coating materials and their applications on concrete surfaces

Coating material	Mechanism of protection	Key chemistry involved	Application	Reference
Nano-silica (SiO ₂) incorporated with PDMS	Surface roughness at the nanoscale and low surface energy due to chemical modifications	These agents react with the silanol groups on the nano-silica surface, replacing them with hydrophobic groups	Improves UV aging resistance, saltwater immersion performance	3
Nano-titanium dioxide (TiO ₂) modified by fluorinated compounds	Water repellence, dirt resistance, chemical and environmental protection	Treated with silane-based compounds, fluorinated alkyl chains, or other hydrophobic agents	Lowers surface energy, provides micro-nano roughness, enables high water contact angles (>150°), reducing water ingress, capillary absorption	30
Nano-calcium carbonate (CaCO ₃) combined with fluoropolymers	It provides a high surface area for interaction and dispersion in coatings or composites	These molecules attach to the surface of CaCO ₃ <i>via</i> chemical or physical bonds, replacing hydrophilic groups with hydrophobic ones	Improved durability, self-cleaning properties	31
Hexamethyldisilazane (HMDS)	It can form a monolayer on surfaces, providing uniform coverage and consistent hydrophobicity	The trimethylsilyl groups create a low-energy surface, which minimizes the interaction between water molecules and the surface	Restricting water penetration, surface treatment to reduce water absorption	32
Polymethyl methacrylate (PMMA)	The presence of nonpolar methyl groups (-CH ₃) and ester group (-COOCH ₃) in its polymer backbone. These groups lack polar or hydrophilic functional moieties, resulting in low affinity for water molecules	It is composed of long chains of methyl methacrylate monomers, which create a highly stable structure	Good tensile strength, protective coating, binder, and surface modifier	33
Trimethylchlorosilane (TMCS)	Mechanism based on its chemical reactivity with hydroxyl groups (-OH) present on surfaces, such as silica, glass, or cellulose, forming a hydrophobic silane layer	TMCS reacts <i>via</i> a silylation process, where its silicon atom forms a covalent bond with the oxygen of the hydroxyl group, releasing hydrochloric acid (HCl) as a byproduct	Used as a silylating agent to modify surfaces by attaching hydrophobic trimethylsilyl (TMS) groups and porous materials. It is employed for surface hydrophobization and protective treatments	34
Tetraethylorthosilicate (TEOS) mixed with fluoroalkyl silane (FAS)	The hydrophobic layer formed by the functionalized silica network resists moisture penetration and prevents water interaction with the substrate	The silanol groups formed during hydrolysis undergo condensation, leading to the formation of Si-O-Si bonds (siloxane bonds) and the release of water or ethanol	Used in protective coatings, antifouling surfaces, microelectronics and sensors, and automotive and aerospace applications	35
Polydimethylsiloxane (PDMS)	When applied to a substrate, PDMS forms a thin, uniform film that acts as a barrier to water and moisture	The -CH ₃ groups on the PDMS polymer are nonpolar and repel water molecules, minimizing water interaction with the surface	Used in spin-coating, dip-coating, or spray coating, followed by curing to form a stable hydrophobic layer	25

involved, and applications. The materials used for hydrophobic coatings, include nano-silica (SiO₂), nano-titanium dioxide (TiO₂), and polymers such as PMMA (polymethyl methacrylate) and PDMS (polydimethylsiloxane). Moreover, Table 1 describes how each material achieves hydrophobicity, such as through surface roughness, chemical modification, or forming protective layers.

2.3 Anti-microbial superhydrophobic coatings for concrete structures

Microbial activity can influence the durability of building materials through various mechanisms of biodeterioration.³⁶

The tendency of microbial activity depends on the type and extent of microbial growth, the type of colonised material, and the level of pollution.³⁷ Antimicrobial superhydrophobic coatings on concrete structures provide dual benefits by both repelling water and resisting microbial growth.³⁸ It has been observed that their decline in structural capacity over time primarily results from chloride ingress *via* six transport processes: adsorption, diffusion, binding, penetration, capillary action, and dispersion. This process causes steel corrosion, concrete cracking, loss of bond and spalling.⁶ Among the causes of structural decay, biologically induced deterioration is notably significant in harsh environments, a phenomenon known as microbiologically induced concrete corrosion (MICC).³⁹ This is



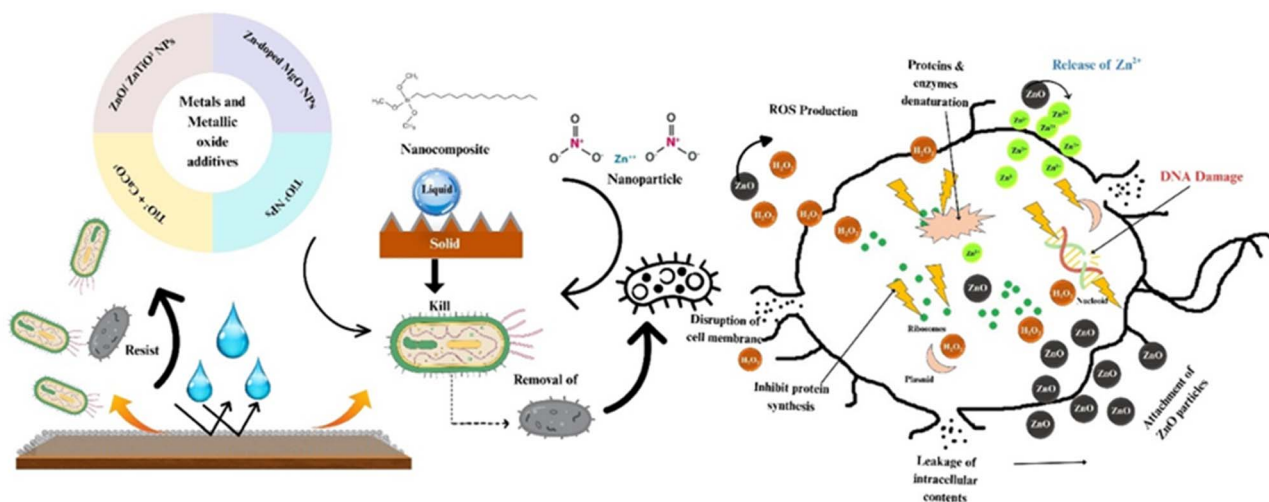


Fig. 7 Schematic of the antimicrobial mechanism of a superhydrophobic surface based on ZnO nanoparticles.

a major concrete-damaging process that significantly threatens the durability and lifespan of sanitary sewer infrastructure elements, including pipes, junctions, manholes, and pump stations, leading to substantial cost implications.⁴⁰ The main groups associated with MICC include sulphate-reducing bacteria and archaea, acid-producing bacteria, thiosulphate-reducing bacteria, iron-reducing bacteria, iron-oxidising bacteria, nitrate-reducing bacteria, and methanogenic archaea.⁴¹

It has been reported that antimicrobial agents work through various mechanisms, such as electrostatic interactions, the production of reactive oxygen species (ROS), and the release of metal ions or metal nanoparticle ions.^{42,43} These mechanisms typically target and weaken the bacterial cell wall, leading to bacterial cell death.⁴⁴

ZnO nanoparticles have demonstrated antimicrobial activity against various microbial species.⁴⁵ Kumar *et al.* reported that ZnO can chemically and physically interfere with bacteria and their further growth. Chemically, ZnO has the ability to react with the bacterial cell, thereby producing photo-induced ROS, and form and release H_2O_2 and Zn^{2+} ions, as shown in Fig. 7. These products damage the bacterial cell membrane and DNA, causing cell death.⁴⁶ ZnO nanoparticle coatings have been found to improve the durability of stone surfaces against fungal attack (such as *Aspergillus niger* and *Penicillium* sp.) by generating ROS when exposed to UV light.⁴⁷ Ruffolo and La Russa investigated the efficiency of ZnO and ZnTiO_3 nanocoatings on stone heritage samples and found that ZnTiO_3 provided higher inhibition than ZnO, even though both are hydrophobic and photocatalytic. The use of Zn-doped MgO nanoparticles (NPs) produced *via* the sol-gel method as antifungal coatings on dolomitic and calcite stones has been reported. These coatings aim to protect surfaces against fungi such as *Aspergillus niger*, *Penicillium oxalicum*, *Paraconiothyrium* sp., and *Pestalotiopsis maculans*, which are active in the bio-weathering of stone.⁴⁸

In another instance, Yang *et al.* described a superhydrophobic coating made from fluorinated silica

nanocomposites, which include fumed nano- SiO_2 and fly-ash drifting beads (FDB). They are modified with 1H,1H,2H,2H-perfluorooctyltrimethoxysilane (FAS-13) and used with poly(vinyl alcohol) as a binder. The coating is applied using a low-pressure sprayer to penetrate concrete pores through capillary action. The optimized coating achieves a water contact angle of 162.4° and sliding angle of 3° , reducing water absorption by 72.03% in deionized water and 80.11% in 3.5 wt% NaCl solution over seven days. Antibacterial evaluations using the spread plate method reveal the reduced adhesion of *Escherichia coli* and *Staphylococcus epidermidis*, with inhibition rates of 84.57% and 90.43% respectively, which is attributed to the non-wetting surface preventing biofilm formation. This coating offers a practical, eco-friendly strategy for enhancing concrete durability in challenging environments.⁴⁹

Titanium dioxide (TiO_2) is recognised as a photocatalyst and is used in self-cleaning tiles, glass, windows, *etc.*⁵⁰ Vishwakarma *et al.* reported that fly ash modified with TiO_2 -nanoparticles as well as mortar with $\text{TiO}_2 + \text{CaCO}_3$ NPs, exhibited its efficacy in antibacterial activities against *Pseudomonas*, *Fusarium*, algae, blue-green algae, and manganese oxidizing bacteria. Vishwakarma *et al.* concluded that adding 2% TiO_2 to fly ash mortar enhanced antibacterial activity by reducing pH levels, and the oxidation of sulfur further helped inhibit bacterial growth.⁵¹

2.4 Concrete substrate compatibility and surface preparation

Superhydrophobic modification of concrete includes two approaches: surface superhydrophobic modification and bulk superhydrophobic modification.⁵² Surface superhydrophobic modification is typically achieved through coating or impregnation. Nevertheless, superhydrophobic coatings often suffer from drawbacks such as poor aging resistance, susceptibility to peeling, and inadequate breathability, which increase the costs associated with subsequent repairs.⁵³ Bulk superhydrophobic modification involves directly incorporating low-surface-energy



Table 2 Comparative performance of superhydrophobic coating systems for concrete

Coating material	Hydrophobicity/wettability	Barrier performance	Durability properties	References
Silane/siloxane	WCA 130°–145° SA < 10° CAH low	Water absorption reduction: 50–70% Chloride ingress: 70–80% Carbonation: moderate reduction	Freeze thaw: good Abrasion: poor Adhesion: N/A	58
Polyurethane-based coatings	WCA 90°–130° SA < 10° CAH medium–high	Water absorption reduction: >90% Chloride ingress: >85% Carbonation: excellent reduction	Freeze thaw: excellent Abrasion: excellent Adhesion: 2–3 MPa (megapascals)	59
Epoxy-based coatings	WCA 90°–140° SA 5°–6° CAH very high	Water absorption reduction: >95% Chloride ingress: >85% Carbonation: excellent reduction	Freeze thaw: excellent Abrasion: excellent Adhesion: 2.5–3.5 MPa	60
Fluorosilane-functionalized Al ₂ O ₃	WCA 130°–160° SA 7°–8° CAH high	Water absorption reduction: >90% Chloride ingress: >80% Carbonation: high reduction	Freeze thaw: excellent Abrasion: good Adhesion: 1.5–2 MPa	61
PDMS-based nanocomposite coating	WCA 150°–158° SA 6°–7° CAH medium	Water absorption reduction: 65–85% Chloride ingress: >70% Carbonation: moderate	Freeze thaw: good Abrasion: good Adhesion: 1–1.8 MPa	62

Table 3 Mechanism-based comparison of major concrete protection strategies

Protection strategies	Mechanism of action	Typical penetration depth	Permeability/breathability	References
Film-forming surface coatings	Formation of a continuous barrier layer on the concrete surface; water repellency <i>via</i> surface roughness and low surface energy	50–500 μm (film thickness). Minimal substrate penetration	Often reduced vapor permeability; limited breathability	63
Penetrating hydrophobic impregnation/sealers	Diffusion of low-viscosity hydrophobic agents into pore walls, forming a water-repellent monolayer without pore blockage	1–10 mm (depth varies with substrate porosity, product viscosity, and application)	Largely preserved vapor permeability; good breathability	64
Pore-blocking/densification	Deposition of solid particles or precipitation of reaction products (<i>e.g.</i> , C–S–H) within the pore structure, physically reducing porosity and permeability	1–30 mm (can achieve significant depth for slurry-based or reactive penetrants)	Significantly reduced vapor permeability	60

materials (such as silanes, siloxanes, and stearic acid) into the concrete mix to achieve an overall superhydrophobic effect in the concrete.⁵⁴

For foamed concrete, most of the superhydrophobic research has been focused on surface modification, while less was on bulk modification due to the high difficulty of its preparation.⁵⁵ Shi *et al.* utilized an isobutyltriethoxysilane (IBTS) and graphene oxide/silane (GO/IBTS) composite emulsion to perform coating and immersion treatments on foamed concrete, reducing its water absorption by 75% and 82%, respectively.⁵⁶ Lu *et al.* developed a self-healing superhydrophobic coating using hydrophobic silica, silicone sealant, and epoxy resin. Gao *et al.* applied a silane emulsion to the surface of foamed concrete, endowing the specimens with excellent anti-icing properties.⁵⁷

Table 2 presents a comparative analysis of the performance of various superhydrophobic coating systems applied to concrete, evaluating five different materials. This comparison highlights the trade-offs among the coatings, with some exhibiting excellent superhydrophobicity and others emphasizing barrier protection or mechanical durability, thereby aiding the selection of appropriate systems to enhance the longevity of concrete against environmental degradation.

Table 3 presents a mechanism-based comparison of the three major categories of concrete protection strategies commonly used to enhance durability and resist environmental degradation. It is an overview of a framework for understanding the trade-offs among different protection strategies and supports the informed selection of concrete protection systems based on exposure conditions and durability requirements.



3 Nanocomposite frameworks for designing superhydrophobic coatings

Nanocomposites are composite materials having one of their phases with dimensions in the nanometer range.⁶⁵ Typically, they consist of multiple phases, with one phase within the nanoscale range of approximately 1 nm to 100 nm. At this scale, materials such as carbon, silicon, and metals display distinct physical properties, since 1 nm (1×10^{-9} m) is one-millionth of a millimeter.⁶⁶ These nanocomposite materials are highly promising for creating superhydrophobic coatings with enhanced durability, reduced environmental impact, and improved self-cleaning capabilities.⁶⁷ They are widely used in the packaging, aerospace, automotive, electronics, semiconductor, energy, construction, and cosmetics sectors. The incorporation of nanoparticles such as silica, titanium dioxide, or carbon nanotubes into a polymer matrix results in a rough surface with a chemical composition that imparts a super-low surface energy and high hydrophobicity, facilitating self-cleaning properties.⁶⁸ Functionalization of these nanocomposites can lead to the development of water-repellent fabrics, anti-fogging surfaces, and corrosion-resistant coatings, showcasing their potential to enhance durability and functionality.⁶⁹

3.1 Structural and functional classification of nanocomposites

Nanoparticles and nanofibers can be categorized according to their size, composition, aspect ratio, and electron microscopy images, which helps to elucidate their effects on nanocomposite properties.⁷⁰ Due to these characteristics, nanocomposites are excellent substitutes for micro-composites and monolithic materials. They are made up of two or more distinct phases with different chemical and physical characteristics, separated by a clear interface.⁷¹ These composite materials have superior properties compared to conventional composite materials and have diverse applications in various areas, including surface coatings for the preservation of concrete and heritage structures.⁷² Nanocomposites are categorized based on the types of matrix materials used in their formulation. Typically, they fall into four main categories according to their matrix material: metal-based, polymer-based, carbon-based, and hybrid materials.⁷³ Table 4 focuses on the different types of nanocomposites used for superhydrophobic coatings, including their characteristics, advantages, typical reinforcements and case studies.

3.1.1 Polymer-based nanocomposites. Polymer matrix nanocomposites (PMCs) are recognized as materials with notable characteristics. Polymers provide numerous benefits, including high durability, lightweight properties, ease of processing, resistance to corrosion, ductility, and affordability.⁹³ However, they generally show inferior mechanical, thermal, and electrical properties compared to ceramics and metals. The physicochemical stability of nanocomposites (PMCs) presents a considerable challenge, mainly due to the complexity of the interfacial zones between the nanoparticles and the polymer

matrices.⁷⁴ These small scales create a large specific surface area, enhancing the significance of polymer–nanoparticle interactions. Due to their polymer-based matrix combined with nano-additives serving as reinforcing materials, these are known as polymer nanocomposites.^{75,76} The additives can be one-dimensional (such as nanotubes and fibers), two-dimensional (layered materials such as clay), or three-dimensional (in the form of spherical particles). The polymer matrix, whether incorporated or formed *in situ* with inorganic nanoparticles, has been extensively studied for developing nanostructures and enhancing waterborne coatings.⁹⁴ The addition of inorganic nanoparticles can improve the waterproofing, mechanical, thermal, electrical, optical, or adhesive properties of the polymeric matrix, as well as some other functional properties.⁹⁵ Martinez *et al.* developed photocatalytic coatings for building materials using TiO₂ nanoparticles incorporated in a polymer matrix-based coating. The photocatalytic coating is suitable for applications to degrade benzene, toluene, ethylbenzene, and *o-m-p*-xylenes.⁹⁶ Due to their outstanding thermal, mechanical, and durability properties, polymer matrix nanocomposites (PMCs) offer functional benefits for the construction industry. The addition of nanoparticles such as nanoclay, carbon nanotubes, graphene, nanosilica, or metal oxides into polymer matrices facilitates the creation of coatings with tailored properties, including self-cleaning, anti-microbial, and antifouling properties.^{77,78}

3.1.2 Metal-based nanocomposites. Metal matrix nanocomposites (MMNCs) are materials composed of a ductile metal or alloy matrix, which serves as a base for embedding nanoparticle reinforcements.⁸⁰ The mechanical, chemical, and physical properties of these composites, consisting of a metal or alloy matrix filled with nanoparticles, are entirely different from those of the matrix material.⁷⁵ Researchers have recently explored metal matrix nanocomposites for their exceptional properties, achieved through the dispersion of nanoparticles, which can be applied in various structural applications.⁸¹ These nanoparticles act as an obstruction to displacement movement, thereby improving mechanical features. Common methods for processing metal matrix nanocomposites include traditional techniques such as spray pyrolysis, liquid metal infiltration, vapor methods, rapid solidification, electrodeposition, and chemical processes such as colloidal and sol-gel methods.⁸²

In another instance, Gu *et al.* developed a multilayer superhydrophobic coating using low-surface-energy silane, SiO₂ particles, and epoxy resin. The coating exhibits excellent impermeability and durability, with a 92% improvement in chloride ion resistance compared with untreated concrete. In addition, enhancing the surface roughness or constructing micro-nanostructures on the surface can significantly augment the hydrophobic characteristics of the coating.⁹⁷

3.1.3 Carbon-based nanocomposites. Carbon nanocomposites (CNCs) are innovative materials that consist of carbon-based structures at the nanoscale, representing the intersection of carbon science and nanotechnology.⁸⁴ CNCs are formulated by integrating carbonaceous materials with various nanostructures, which are critical in determining their properties and functionalities. Choosing and combining these



Table 4 Comparison of various case studies based on different types of nanocomposites

Types of nanocomposites	Matrix materials	Characteristics	Matrix reinforcements	Findings from case studies	Applications	References
Polymer-based nanocomposites (PMCs)	Polymers (e.g., various resins, silanes)	Lightweight, corrosion resistance, improved thermal & mechanical properties	Nanoclay, carbon nanotubes (CNTs), graphene, nanosilica, metal oxides	Silane/clay nanocomposites (Cloisite 20A & I.30P); ~50% reduction in moisture permeability; superior barrier with high-aspect-ratio Cloisite 20A	Self-cleaning, antimicrobial, antifouling coatings; concrete protection and reduced moisture permeability	74–79
Metal-based nanocomposites (MMNCs)	Metals or alloys (ductile matrix)	Enhanced mechanical strength, thermal stability, resistance to dislocation movement	Zero-dimensional (core-shell), one-dimensional (nanotubes), two-dimensional (laminar); various nanoparticles	Different reinforcement phases classified by <i>in situ</i> vs. <i>ex situ</i> fabrication methods for better uniformity/bonding	Tailored mechanical, catalytic, electrochemical properties <i>via in situ</i> and <i>ex situ</i> fabrication	75 and 80–83
Carbon-based nanocomposites (CNCs)	Carbon-based structures (e.g., graphene, CNTs)	High surface area, tunable electrical & mechanical properties, functionalization improves dispersion	Graphene, CNTs, nanodiamonds, graphene oxide (GO), integrated with metal oxides/polymers	Functionalized graphene oxide (GO) forms hydrophobic protective coat; 83.4% corrosion inhibition efficiency at 20 mg L ⁻¹ ; graphene nanoplates (GNPs) create carbon-doped protective layer	Corrosion protection, long-term resistance in chloride-rich environments	84–88
Hybrid-material-based nanocomposites	Combination of organic & inorganic (polymeric, ceramic, metallic matrices)	Synergistic mechanical strength, chemical stability, UV resistance	CNTs, graphene, metal oxides (TiO ₂ , ZnO, SiO ₂), metallic nanoparticles (Ag, Cu)	SiO ₂ -TiO ₂ hybrid nanoparticles <i>via sol-gel</i> ; alkoxide mixing; oxalic acid & surfactants prevent agglomeration/cracks; improved consolidation on carbonate stones	Self-cleaning, antimicrobial, UV-resistant coatings; crack-free protective coatings for stone surfaces	89–92

components is vital for effectively customizing CNCs for specific applications.⁸⁵ For instance, different carbon allotropes, such as graphene, carbon nanotubes (CNTs), and nanodiamonds, are integrated with other nanomaterials such as metal oxides, polymers, or nanoparticles to achieve the desired attributes.⁸⁶ Nanocarbon materials, primarily allotropes such as graphene and its derivatives, have established a prominent role and are regarded as promising materials within the scientific community. Functionalizing these materials is crucial for enhancing their performance.⁸⁷ In another instance, chemical functionalization of graphene as a nanomaterial involves modifying its surface, typically by introducing oxygen-containing groups such as hydroxyl, carboxyl, epoxy, and carbonyl *via* oxidation to produce graphene oxide (GO). This functionalization can be implemented either through covalent methods such as oxidation to graphene oxide or silane grafting or non-covalent approaches using polymers or superplasticizers, introducing surface functional groups that enhance its dispersion and interfacial bonding with cement hydration products.⁹⁸

Graphene oxide (GO), as a promising 2D nano-material, is the product of chemical exfoliation of graphite that has homogenous and stable dispersion in aqueous media.⁹⁹ Due to its good dispersibility in water and its high surface area of about $2600 \text{ m}^2 \text{ g}^{-1}$, GO could be a potential alternative for the surface protection of concrete.¹⁰⁰ In recent years, there have been some pioneering studies on the application of GO with building materials to improve their performances. Gong *et al.* reported that the introduction of 0.03% by cement weight of GO nano-sheets into cement paste increased its compressive strength and tensile strength by more than 40%.¹⁰¹ Similarly, Pan *et al.* described that the introduction of 0.05% by cement weight of GO into cement paste increased its compressive strength by 15–33% and flexural strength by 41–59%.¹⁰² Furthermore, Li *et al.* investigated the dispersion of GO in simulated pore solution and cement paste and observed severe GO aggregation in the presence of divalent calcium ions in both pore solution and cement paste.¹⁰³

3.1.4 Hybrid-material-based nanocomposites. Hybrid materials are highly valued for their exceptional mechanical strength, chemical stability, thermo-sensitivity, optical properties, corrosion resistance, and electrical and fire retardancy.⁸⁹ This concept is further exemplified by hybrid organic-inorganic nanomaterials, which combine organic and inorganic components to achieve synergistic properties. Nanoparticles are particularly interesting because they promote the synergistic interactions between organic components of hybrid material coatings and inorganic compounds on heritage substrate materials, improving their protective capabilities and enhancing the coating performance. Nanosilica (n-SiO₂), nanotitanium dioxide (n-TiO₂), nano-zinc oxide (n-ZnO), carbon nanotubes (CNTs), graphene oxide, and nano-aluminium oxide (n-Al₂O₃) are the most popular materials, and hybrid materials containing combinations of these nanomaterials have been used for coating concrete structures.²⁶ Common synthesis techniques include sol-gel processing, electrodeposition, and spray coating, all of which encourage uniform dispersion and effective adhesion. These materials are used in various

industries, including aerospace, marine, automotive, health-care, and electronics, offering advantages such as self-cleaning capabilities, antimicrobial protection, and UV resistance.⁹⁰

Mahmoud *et al.* demonstrated a 74.6% reduction in water absorption rate by incorporating n-SiO₂ and n-Al₂O₃ into a sol-gel system dispersed in a tetraethoxysilane (TEOS) polymer solution. The results reported by these authors were promising, achieving super-hydrophobicity with a maximum reported contact angle (CA) of 135°. ¹⁰⁴

4 Criteria for selecting suitable materials

Superhydrophobic surfaces have static contact angles greater than 150° and sliding angles less than 10°. It is well known that the wettability of a solid surface depends on two main factors: surface roughness and surface chemistry.¹⁰⁵ The energy is determined by the chemical composition of the surface, which significantly influences its wettability. The primary method for creating superhydrophobic surfaces involves patterning roughness on a solid surface, followed by applying a thin layer of hydrophobic coating material.¹⁰⁶ Hydrophobic chemistry typically relies on fluoropolymers or siloxanes with low surface energy.

Enhancing the durability of superhydrophobic surfaces is an important issue for self-cleaning and anti-corrosion properties. However, most of the superhydrophobic coatings obtained by the reported methodologies possess limited abrasion resistance.¹⁰⁷ The evaluation of the change in static contact angle, contact angle hysteresis, and surface friction coefficient determines the abrasion resistance. Nanoparticles (NPs) usually regulate and control the nanoscale roughness of coated surfaces. SiO₂ NPs, characterized by abrasion resistance, low-cost availability, and a variety of particle nano-sizes, are a common choice for fabricating transparent superhydrophobic surfaces.¹⁰⁸

In another instance, Ramachandran *et al.* controlled entropic molecular interactions to design a novel icephobic concrete.¹⁰⁹ This type of concrete showed a low ice adhesion strength and could repel incoming water droplets at –5 °C. Zhao *et al.* fabricated a superhydrophobic surface on concrete for anti-icing.¹¹⁰ She *et al.* developed a superhydrophobic concrete surface by spraying modified silica gel to simultaneously construct a hierarchical micro/nanostructure and lower the surface energy.¹¹¹

Table 5 lists different nanocomposites used to develop superhydrophobic coatings, categorized by material type, synthesis methods, and outcomes. It includes various categories of nanocomposites, including thermoplastics, thermosets, elastomers, metals, carbon-based materials, and hybrid materials. This synthesis process produces coatings suitable for a range of industrial and functional uses.

Additionally, Table 6 comprehensively summarizes durability tests that are directly relevant to evaluating the long-term performance of superhydrophobic coatings for construction applications. These tests are highly relevant as they simulate





Table 5 Overview of the synthesis processes of superhydrophobic coatings

Type of nanocomposite	Categories	Superhydrophobic coating	Synthesis process techniques	Result	References
Polypropylene/clay nanocomposites	Thermoplastic polymer nanocomposite	Surface roughness enhancement, low surface energy modification, spray coating or dip coating techniques	Clay modification, melt compounding, dispersion & exfoliation	Automotive coating, construction & architectural coating, aerospace coating	112
Polyethylene/silica nanocomposites	Thermoplastic polymer nanocomposite	Layer-by-layer (LbL) deposition, silane modification	Silica surface modification, Polyethylene and silica mixing, extrusion and cooling	Self-cleaning, anti-fogging, corrosion-proof	113
Epoxy/carbon nanotube nanocomposites	Thermoset polymer nanocomposite	CNT dispersion, coating deposition	Ultrasonication, high-shear mixing, three-roll milling	Electronics and electrical applications, energy storage and batteries	114
Vinyl ester/silica nanocomposites	Thermoset polymer nanocomposite	Surface modification of silica nanoparticles, dispersion of silica in vinyl ester resin	Sol-gel method, surface modification, dispersion of silica	Chemical and corrosion-resistant construction	115
Natural rubber/carbon black nanocomposites	Elastomer polymer nanocomposite	Surface roughness, low surface energy	Melt blending, <i>in situ</i> polymerization, sol-gel method, electrospinning method	UV protection & weather resistance, anti-static & conductive paints	116
TiO ₂ nanocomposites	Metal-based nanocomposite	Anti-corrosion & anti-icing coatings, durability improvement	Hydrothermal method, sol-gel method, precipitation method, electrochemical deposition, chemical vapor deposition	Paints and coatings, anti-fogging coatings	117
Al ₂ O ₃ nanocomposites	Metal-based nanocomposite	Corrosion & chemical protection, electronic & sensor protection	Sol-gel method, Co-precipitation method, combustion synthesis	Wear-resistant coatings for electronic devices, self-cleaning & scratch-resistant coatings	118
Graphene-based nanocomposite	Carbon-based nanocomposite	High surface area, layer-by-layer assembly, spray coating	<i>In situ</i> polymerization, melt blending, exfoliation adsorption, chemical vapor deposition	Pollutant removal, coatings, filtration membranes	119
Carbon nanotube nanocomposites	Carbon-based nanocomposite	Low surface energy, surface roughness, layer-by-layer assembly, chemical vapor deposition	Carbon nanotube (CNT) synthesis methods, CNT functionalization, dispersion of CNTs, fabrication of CNT nanocomposites	Aerospace & automotive industry, biomedical & healthcare, structural & coating applications	119
Ni-TiO ₂ nanocomposites	Hybrid-material-based nanocomposites	Water-repellent & self-cleaning surfaces, antibacterial & antifouling coatings, anti-corrosion coatings, spray or dip-coating of nanoparticle suspensions	Sol-gel method, hydrothermal method, Co-precipitation method, electrochemical deposition	Photocatalysis & environmental remediation, hydrogen production & energy applications, catalysis & industrial applications	120
Cu-PDMS (polydimethylsiloxane) nanocomposites	Hybrid-material-based nanocomposites	Surface modification, fabrication methods, surface roughness	direct mixing method, <i>in situ</i> nanoparticle formation in PDMS	Flexible & stretchable electronics, thermal management & heat dissipation, antimicrobial coatings & surfaces	121



Table 6 Factors demonstrating the wettability and durability of superhydrophobic coating materials

Factors	Significance	Overview of the case study	References
Wettability tests	<ul style="list-style-type: none"> Greater than 150°, exhibiting excellent water-repellent properties and significantly reducing surface degradation It is considered when surfaces are not atomically smooth, contaminated, swelled, or reoriented A sliding angle of less than 10° is a key characteristic of superhydrophobic surfaces Water droplets exhibit “rolling off” behavior with a low sliding angle, typically below 10°, due to a high water contact angle (greater than 150°) and low surface energy A contact angle hysteresis of less than 5° is ideal for making a surface superhydrophobic It accounts for the adhesiveness of a water droplet with the substrate, and it is the difference between the advancing angle (θ_A) and the receding angle (θ_R) It can be used to monitor changes in water repellency over time The liquid typically interacts very little with the surface due to the high degree of water-repellency, meaning it does not wet the surface but forms a droplet, resulting in minimal or no contact between the liquid and the coating 	<ul style="list-style-type: none"> The superhydrophobic coatings were created by spraying an SiO₂-ethanol suspension onto a dip-coated epoxy resin film on a glass slide. The results indicated that the water contact angle (CA) of the coating reached 154.7° Fabrication of porous polymer coatings by chemical vapor deposition resulted in a superhydrophobic coating that has a rigid elastic and micro-nanostructure; its CA was 157°, and sliding angle (SA) was 1° 	110
Water contact angle (WCA) test	<ul style="list-style-type: none"> A contact angle hysteresis of less than 5° is ideal for making a surface superhydrophobic 	<ul style="list-style-type: none"> The theory is applied to predicting contact-angle hysteresis on rough surfaces from the hysteresis observed on smooth surfaces and therefore relevant to predicting roll-off angles for droplets on tilted surfaces 	122
Water sliding angle (WSA) test	<ul style="list-style-type: none"> It can be used to monitor changes in water repellency over time 	<ul style="list-style-type: none"> Karsten tube tests revealed zero water penetration on hydrophobized samples 	124
Contact angle hysteresis (CAH) test	<ul style="list-style-type: none"> The liquid typically interacts very little with the surface due to the high degree of water-repellency, meaning it does not wet the surface but forms a droplet, resulting in minimal or no contact between the liquid and the coating Coated sandpaper with grit sizes of 240, 400, 800, 1000, and 1500 expresses super-hydrophobic properties. It exhibits a high water contact angle between 158° and 165° and a low sliding angle ranging from 10° to 2° 	<ul style="list-style-type: none"> The creation of superhydrophobic surfaces (SHS) increases the surface roughness. Sandpaper itself possesses an intrinsic surface roughness formed by abrasive particles, which are securely attached to its surface, reinforcing the robustness of its surface roughness 	125
Durability tests	<ul style="list-style-type: none"> It is characterized by a combination of high surface roughness and low surface energy, which allows water to form droplets and roll off easily Micro/nano hierarchical structures provide a valid method to strengthen the mechanical stability of superhydrophobic surfaces 	<ul style="list-style-type: none"> Hydrophobic SiO₂ nanoparticles using tetraethyl orthosilicate, NH₄OH, H₂O and methyltriethoxysilane in ethanol, constructing a robust surface structure comprising substrate, bonding layer and superhydrophobic layer 	62
Karsten tube analysis test	<ul style="list-style-type: none"> Superhydrophobic surfaces create an air layer between the surface and water, which further minimizes contact with corrosive liquids Minimizes contact between corrosive substances and the underlying material, thus slowing down or preventing corrosion 	<ul style="list-style-type: none"> The combination of superhydrophobicity and low conductivity is crucial for enhancing corrosion resistance. Additionally, the inclusion of SiO₂ nanoparticles in a PTFE superhydrophobic coating enhances corrosion protection by filling the defects and pores within the coating 	126
Sandpaper abrasion test	<ul style="list-style-type: none"> Water-repellent capacity depends on the micro- or nano-structured surface of the coating, which is essential for superhydrophobicity Some superhydrophobic coatings, especially fluoropolymer-based ones, can withstand moderate water impact 	<ul style="list-style-type: none"> Altering a magnesium oxychloride cement composite with a superhydrophobic coating greatly enhanced its water resistance 	127
Water uptake test			
Corrosion resistance test			
Water impact resistance test			

real-world mechanical and environmental stresses that superhydrophobic surfaces might encounter. Sandpaper abrasion and friction wear (ball-on-plate) tests assess resistance to mechanical wear and surface damage caused by prolonged exposure to high-kinetic-energy water flows and impact damage from falling objects, which are critical challenges for building surfaces. The waterfall/jet test simulates prolonged rain exposure and high-impact water flow, verifying whether the coating can retain its water-repellent behavior under realistic environmental conditions where the kinetic energy of water can destroy the surface roughness and induce wetting. Adhesion-related durability, examined by tape peeling and pull-off strength tests, ensures strong bonding between the coating and substrate. Compared to many commercially available water-repellent coatings, the referenced results demonstrate a broader and more rigorous durability assessment, particularly in tribological and impact-related aspects.

5 Fabrication techniques for superhydrophobic coatings on concrete

Concrete is naturally hydrophilic, allowing water and corrosive ions to easily penetrate its pores, which diminishes the durability of structures.¹²⁸ To combat this, superhydrophobic modification is commonly employed to reduce/limit water infiltration and enhance durability.^{129,130} Most superhydrophobic coatings are developed by creating rough surfaces through multistep processes.¹³¹ Recent studies categorize concrete surface treatment methods into three primary types: surface coatings, pore-blocking treatments, and hydrophobic

impregnation.¹³² Finding suitable materials, simple fabrication techniques, and efficient, durable, eco-friendly superhydrophobic coatings for practical use remains challenging.¹³³ Based on superhydrophobicity principles, various strategies have been devised to create concrete surfaces with suitable topological structures and surface chemical compositions to achieve water repellency.

5.1 Deposition methods for coating materials

The development of superhydrophobic systems has attracted increasing attention because of their numerous practical applications.¹³⁴ These fabrication techniques are generally categorized into four main methods: (1) dip coating by immersing concrete samples into hydrophobic organic solutions; (2) spin coating with a polymer or polymer emulsion mixed with cement applied on the surface; (3) spray coating hydrophobic suspensions enriched with micro/nano particles on the surface; and (4) electrochemical deposition by replicating the delicate micro- and nano-scale surface structures¹²⁸ shown in Fig. 8. These approaches aim to reduce the surface energy and create hierarchical roughness, which enhances water the contact angles and minimizes water absorption. Table 7 briefly compares different fabrication techniques for superhydrophobic coatings with a clear focus on their potential suitability for construction/building applications. Implementing these coatings in the real world is a challenging task. Most of these techniques can only be applied to lab samples, with very few being practical for large-scale infrastructure.¹³⁵

5.1.1 Dip coating technique. Dip coating is a valuable technique for fabricating superhydrophobic coatings. This process involves continuously dipping the substrate into

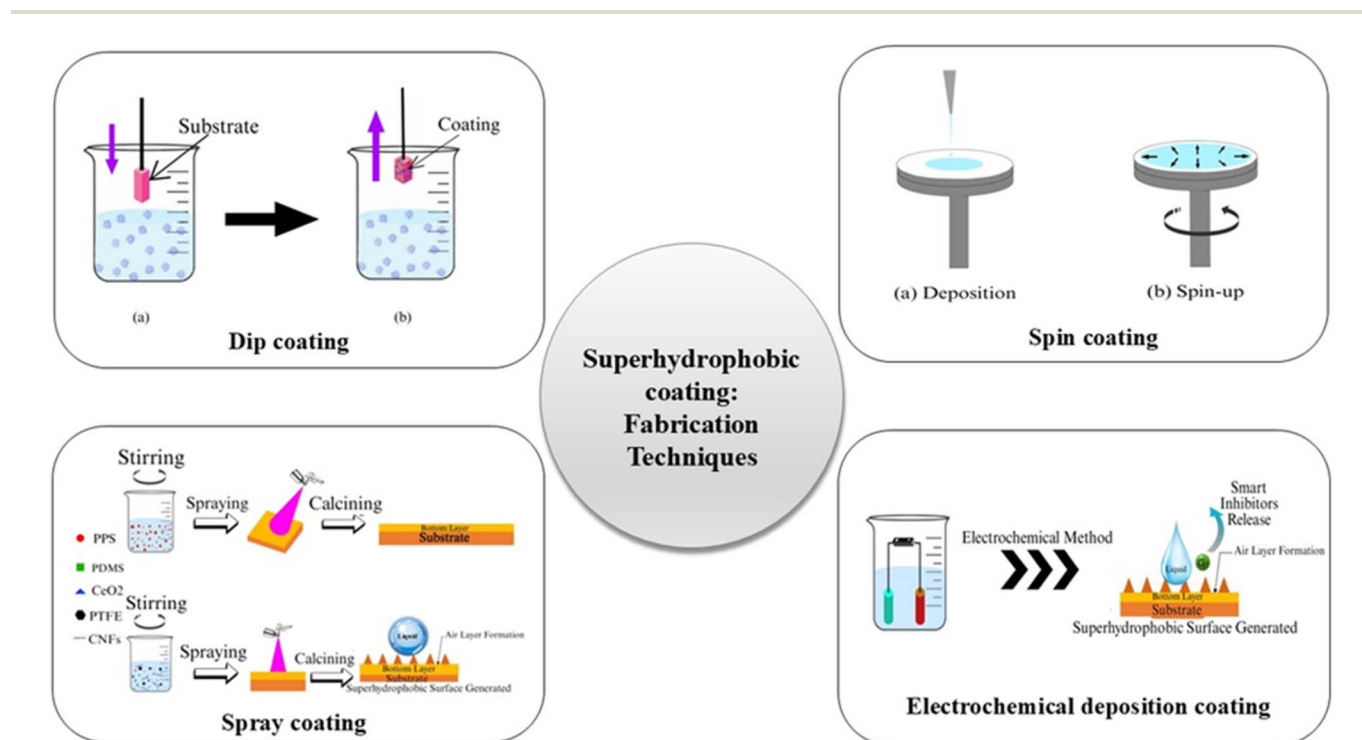


Fig. 8 Different types of fabrication techniques of superhydrophobic coatings.



Table 7 Comparative analysis of the fabrication techniques of advanced concrete coatings

Fabrication technique	Process of fabrication	Materials used	Advantages	Suitability for construction application	References
Dip coating technique	Substrate is immersed in a hydrophobic solution and withdrawn at a controlled speed	Sol-gel systems, polymeric coatings	Low processing temperature, good adhesion, uniform coating on all sides, minimal waste, durable, compact	Suitable only for small components (meshes, fences, small metal parts)	68 and 136
Spin coating technique	Solution is dispensed on a flat substrate, which is spun at high speed (1000–8000 rpm) to spread into a thin uniform film	Hydrophobic electrospun fibers using thermoplastic elastomers	Excellent uniformity and thin films; good control of thickness <i>via</i> speed	Not feasible for building infrastructure, lab-scale only	115, 137 and 138
Spray Coating technique	Hydrophobic suspension is sprayed onto the surface using a spray gun	Polymer solutions, silanes, nanocomposites	Simple, fast, low-cost, automatable, repairable	Highly practical & scalable for large areas <i>e.g.</i> , concrete, steel, bridges	111 and 139
Electrochemical deposition technique	Uses anodic oxidation, galvanic deposition, or anodization to grow micro/nano structures	Metals, alloys, conductive polymers, and ceramics	Precise control of morphology	Promising for corrosion protection, but scalability is limited for large concrete elements	140 and 141
Chemical vapor deposition (CVD) technique	Gas-phase chemical reactions forming thin films	Silanes, fluorosilanes	Highly uniform, durable coatings	Not practical for large concrete surfaces	142
Layer-by-layer (LbL) technique	Alternate adsorption of oppositely charged species	Polymers, nanoparticles	Precise thickness control	Laboratory-based only	143

a solution containing the desired deposition material at a constant speed.¹⁴⁴ When the substrate is immersed in the solution for a specific duration and lifted out, a film is deposited it as it is removed.⁶⁸ The withdrawal or pulling speed determines the film thickness; typically, a higher speed results in a thinner film. Excess solution is removed from the surface during withdrawal.¹⁴⁵ The solvent in the solution evaporates, leaving a coating on the surface. This technique has no self-repairing ability. It involves immersing the substrate into a coating solution and then slowly withdrawing it, allowing a thin, uniform film to form as the solvent evaporates. It is widely used for superhydrophobic coatings because it is simple, low-cost, scalable, and effective for complex or porous surfaces, including concrete or fabrics.¹⁴⁶

This method offers numerous benefits, including the ability to coat both the top and bottom parts of the substrate simultaneously, minimal material waste, compatibility with various materials, high production output, uniform coatings, and coatings that are highly durable, compact, stable, and easily repairable.⁶⁸

5.1.2 Spin coating technique. The spin coating technique generates a thin layer on relatively flat substrates. A solution of the material to be applied is placed onto the substrate, which is then rotated at high speeds ranging from 1000 to 8000 rpm, resulting in a uniform coating.¹⁴⁷ The thickness of the deposited film is determined by the angular velocity, solution viscosity, and spinning duration. The thickness of the film can be modified by adjusting the spin speed or using various photo-resists. This technique is particularly effective on a laboratory scale.

5.1.3 Spray coating technique. In this method, a solution of the coating materials is applied to the substrate using a spray gun. The method generally begins with thorough surface preparation of the concrete, involving high-pressure washing to remove dust and oils, followed by drying and optional light abrasion for better adhesion. Next, a coating suspension is prepared by dispersing nanoparticles in a solvent such as ethanol or isopropanol, incorporating a low-surface-energy modifier such as superhydrophobic agent and an adhesive such as epoxy resin. Application occurs *via* spray coating using a low-pressure spray gun or airbrush.⁶⁹ This approach offers several benefits, including simplicity, wide availability, potential for automation, speed, cost-effectiveness, ease of repair, and non-toxicity.¹³⁹ Additionally, this technique can be utilized on various substrates such as plastics, metals, and fabrics.¹⁴⁸

5.1.4 Electrochemical deposition technique. The electrochemical deposition method stands out as one of the most promising approaches due to its ability to easily control the kinetics of surface feature growth and create diverse morphologies over large surfaces.¹⁴⁰ Electrodeposition is an electrochemical phenomenon that underpins an emerging class of treatments with unique potential to rehabilitate concrete structures. Practical implementations include laboratory-validated field trials and actual repairs of cracked or corroded reinforced concrete, demonstrating effective crack closure, improved corrosion resistance, and minimal pH disruption when using variable or reversed polarity currents for more



Table 8 Applications of green material-based superhydrophobic coatings in surface modifications

Green materials	Nanocomposite incorporating superhydrophobic coating agents	Nanoparticle type	Application	Overall result	Cost & scalability	References
Septiolite	Fatty acids, organosilanes	Silicate clay mineral	Self-cleaning and corrosion protection	Enhances their performance by contributing to robustness, mechanical stability	Low cost; scalable	7
Halloysite	Organosilanes, polymers	Silica and alumina	Create rough surfaces, achieve extreme water repellency	Contributes to the overall hydrophobicity of the coating, leading to higher water contact angles	Low-moderate cost; scalable	151
PDMS	SiO ₂ , TiO ₂	Silver and metal oxides	To enhance adhesion to the substrate and impart hydrophobicity	Exhibits good durability and stability, resisting abrasion, UV radiation, and harsh chemical environments	Moderate cost; scalable	143
ZnO	Stearic acids, silanes	Metal oxide nanomaterial	Decrease the surface energy and increase the surface roughness by reacting with the mixed solution	High water contact angles (WCA), self-cleaning capabilities, and potential antibacterial and UV-blocking effects	Low cost; highly scalable	153
Cinnamic acid	Fluorinated polymers, silanes	Zinc oxide (ZnO) nanoparticles	Antibacterial activity and UV shielding, making surfaces water-repellent	Excellent robustness and water-repellence properties, materials with low surface energy	Moderate cost; scalable	152
Myristic acid	SiO ₂ , TiO ₂ , or Al ₂ O ₃	Solid lipid nanoparticles (SLNs)	To modify surfaces and create water-repellent properties	Becomes highly water-repellent, with water droplets beading up and rolling off easily	Low cost; scalable	142
Bagasse	Dimethyldiethoxysilane (DMDEOS), fatty acids, fluorinated compounds	Silica nanoparticles	Good adhesion and good protective properties that allow it to withstand the diffusion of water vapor	Good anti-fogging, anti-freeze, and anti-bacterial properties	Low cost; highly scalable	154
Egg waste and stearic acid (STA)	SiO ₂ , TiO ₂ , ZnO, MgO	Calcium oxide (CaO) and solid lipid nanoparticles	Environmentally friendly material for fabricating a hydrophobic barrier	Superhydrophobic properties, 4° sliding angle, mechanical resistance towards damage and UV irradiation	Very low cost; scalable	155
Chitosan modified by octadecylamine	Octadecylamine (ODA), fatty acids, fluorinated compounds	Fe ₃ O ₄	To create durable and sustainable superhydrophobic coatings, particularly for textiles	Superhydrophobic properties superoleophilic properties	Moderate cost; scalable	156
Corn husks	Perfluorodecyltriethoxysilane (PTES), PVA (polyvinyl alcohol)	Silica, cellulose nanocrystals, and even metal nanoparticles such as palladium, silver, and copper	Preventing corrosion and rust	De-icing properties, photothermal properties	Low-moderate cost; scalable	23
Rice husk ash	Fluoroalkyl silane (FAS), 1H,1H,2H,2H-perfluorodecyltriethoxysilane	Silica nanoparticles	To create a rough surface, enhancing water repellency and other properties	High water repellency (water contact angles exceeding 150°) and reducing water uptake in materials such as concrete	Low cost; highly scalable	157
Wheat straw	Stearic acid, fatty acids, or silane coupling agents	Nanocellulose, nanolignin, nanosilica, silver nanoparticles	Self-cleaning surfaces	High water repellent properties	Low cost; scalable	113

uniform deposition.¹⁴⁹ However, it is not commonly used for superhydrophobic coatings on concrete surfaces. Superhydrophobicity is typically achieved *via* spray, spin, or sol-gel methods with nanoparticles. These electrochemical processes are facile, rapid, and reproducible. Various electrochemical deposition techniques including anodic oxidation, galvanic deposition, electropolymerization, and electrochemical anodization are commonly employed for material production.¹⁵⁰

5.2 Scalable fabrication approaches

This section will explore superhydrophobic coatings made from different green materials, highlighting their chemical, physical, and environmental considerations. Table 8 shows that nanoparticles have diverse applications, ranging from self-cleaning surfaces and corrosion protection to antibacterial activity, UV shielding, and eco-friendly coatings. Green materials include sepiolite, halloysite, PDMS, ZnO, cinnamic acid, myristic acid, *etc.*, modified by octadecylamine, corn husk, and rice husk, yielding nanoparticles such as silicate clay, silica, alumina, gold and silver, metal oxide, and solid lipid nanoparticles, among others.¹⁵¹ These green materials are agricultural byproducts that can be used as superhydrophobic coating materials for concrete as they are environmentally friendly, cost-effective, and durable. Sepiolite and halloysite are fibrous and tubular clay minerals with abundant silanol (Si-OH) groups and a porous structure, which provide a high specific surface area and active sites for modification, enabling the creation of rough surfaces essential for superhydrophobicity.¹⁵² Their capacity for cation exchange and surface functionalization allows for the stable incorporation of hydrophobic agents, such as octadecylamine, which lowers the surface energy by introducing long hydrocarbon chains, enhancing the water repellence. PDMS (polydimethylsiloxane) serves as a flexible, durable binder that supports the micro-nano roughness needed for superhydrophobicity while offering chemical and mechanical stability.¹⁴² ZnO, cinnamic acid, and myristic acid contribute to surface roughness and hydrophobicity through their inherent chemical properties. Additionally, agricultural waste such as corn husk and rice husk provides eco-friendly, renewable fillers that impart hierarchical surface textures and reduce environmental impact.¹⁴³

6 Tribological performance and durability of nanocomposite-derived superhydrophobic coatings under mechanical stress on concrete materials

Due to its extremely non-wetting properties, a superhydrophobic surface has a wide range of potential applications, including wear resistance, drag reduction, anti-corrosion, anti-icing, and self-cleaning.^{158,159} The long-term effectiveness of superhydrophobic coatings on concrete structures is critically dependent on their tribological performance, including friction, wear resistance, and surface contact mechanics, as shown

in Fig. 9.^{160,161} It illustrates the interplay among surface chemistry, nanocomposite coating structure, and wettability. Surface roughness and low surface free energy are the two key factors in creating a superhydrophobic surface, which are also the main reasons for its excellent tribological performance.¹⁶²

Table 9 comprehensively summarizes the durability tests that are directly relevant to evaluate the water repellent properties of superhydrophobic coatings for construction applications. These tests are particularly relevant as they simulate real-world mechanical and environmental stresses on superhydrophobic surfaces. The sandpaper abrasion and ball-on-plate friction wear tests specifically assess resistance to mechanical wear and surface damage caused by prolonged exposure, high-kinetic energy water jets, impacts from falling objects, and other wear factors critical to building applications. The waterfall/jet test simulates prolonged rain exposure and high-impact water flow, verifying whether the coating can retain its water-repellent behavior under realistic environmental conditions where kinetic energy of water can destroy surface roughness and induce wetting. Adhesion-related durability, examined by tape peeling and pull-off strength tests, ensures strong bonding between the coating and substrate. Compared to many commercially available water-repellent coatings, the referenced results demonstrate a broader and more rigorous durability assessment, particularly in tribological and impact-related aspects.

6.1 Tribological mechanisms in superhydrophobic nanocomposites

Superhydrophobic nanocomposites, particularly formed through the self-assembly of nanostructures such as inorganic micro- and nano-particles or carbon nanotubes, exhibit enhanced tribological properties that contribute to their practical applicability.¹⁶⁸ The development and further enhancement of high-performance, wear-resistant materials will create significant economic and social benefits.¹⁶⁹ Enhancing the tribological properties of materials to reduce wear and friction during the work process can boost the efficiency and prolong the lifespan of machinery, thereby lowering carbon dioxide emissions and reducing resource and energy waste in production and manufacturing processes.¹⁷⁰ Mechanical wear directly affects superhydrophobicity by progressively damaging the hierarchical micro-nano surface structures and/or removing the low-surface-energy chemical groups that are essential for maintaining the Cassie-Baxter wetting state. During abrasion or sliding, the uppermost nano-features are typically worn first, leading to a gradual reduction in surface roughness and trapped air fraction. As a result, the water contact angle (WCA) decreases, while the sliding angle (SA) and contact angle hysteresis (CAH) increase.¹⁷¹

According to Mohammed *et al.*, zirconia (ZrO₂) nanocoatings exhibit excellent tribological characteristics and are also attractive for their electrical and optical properties.¹⁷² In another instance, Zhang *et al.* evaluated the deposition of nano-ZrO₂ film coatings on 304 stainless steel substrates. The nanofilms showed reduced friction coefficients when tested against



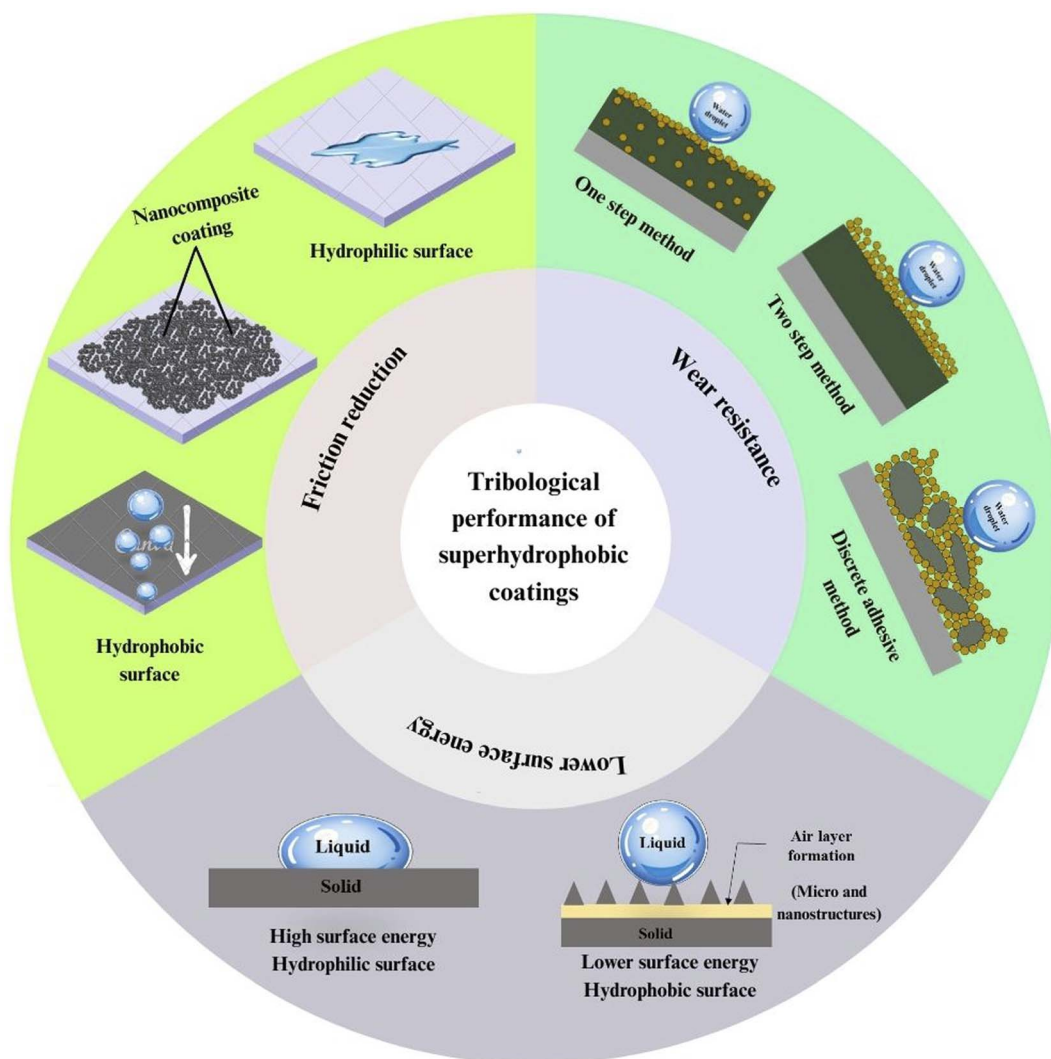


Fig. 9 Schematic of the tribological performance of superhydrophobic coatings.

Table 9 Durability tests of superhydrophobic coatings to evaluate their water repellent properties

Durability tests	Properties	References
Sandpaper abrasion test	It uses a controlled abrasive to measure how the surface of a material withstands wear	163
Friction wear test (ball-on-plate tribometer)	This method uses a tribometer to slide a ball or stylus across the surface under a controlled load and motion	164
Waterfall/jet test	It detects surfaces under long-term water exposure and how different kinetic energies of water impact the surface influence wetting properties	165
Falling weight impact test	A weight is dropped onto the surface to assess its resistance to cracking or delamination	166
Tape peeling test	An adhesive tape is applied and removed, and the surface is inspected for coating removal	167
Pull off strength test	A quantitative method where a dolly is adhered to the coating and pulled off with a controlled force	163

an SiC grinding ball in 5% NaCl solution, distilled water, and dry conditions. Under dry conditions, adhesive and oxidation wear were the main wear mechanisms, whereas in 5% NaCl

solution, corrosive wear was dominant. The coatings exhibited significantly reduced friction coefficients ($\approx 0.25\text{--}0.35$) compared to the uncoated substrates.¹⁷³



Gu *et al.* examined that alumina (Al_2O_3), an oxide ceramic, has been extensively utilized as a coating material owing to its superior wear resistance. The wear behavior of nanostructured alumina coatings on SS304 stainless steel substrates, created *via* atmospheric plasma spraying, was assessed and compared to that of micro-alumina coatings. The nano-alumina coatings exhibited better wear resistance than the micro-coatings under applied normal loads of 30 N to 80 N. Graphene- and CNT-reinforced epoxy nanocomposites, frequently proposed for concrete protection, were evaluated using steel or alumina balls under normal loads of 5–15 N, sliding speeds of $0.05\text{--}0.1\text{ m s}^{-1}$, and sliding distances of 100–500 m.¹⁷⁴

The use of carbon nanocomposites such as graphene and carbon nanotubes (CNTs) in epoxy composites has revolutionized the field of tribology by significantly enhancing the mechanical and tribological properties of these materials.¹⁷⁵ Incorporating graphene into the epoxy matrix improves its mechanical strength and toughness; the high modulus of elasticity of graphene aids in better load distribution, preventing localized stress concentrations that can lead to wear and failure.¹⁷⁶ Studies indicate that graphene-reinforced epoxy exhibits significantly lower wear rates compared to unmodified epoxy. Furthermore, graphene's exceptional tensile strength enhances the load-bearing capacity of epoxy composites, that helps to maintain structural integrity under mechanical stress and make these materials ideal for applications in concrete industries.¹⁷⁷ This mechanism provides superior tribological performance on concrete surfaces through synergistic combination repellency-driven contact minimization, robust interfacial adhesion, and partial integration into the substrate. However, long-term durability remains limited by substrate erosion in highly porous or low-strength concretes under severe mechanical loading.^{169,178}

6.2 Mechanical durability and retention of superhydrophobicity post-stress

The long-term durability of self-assembled nanostructures against mechanical wear, friction, and surface contacts is essential for their practical application in superhydrophobic surfaces.¹¹¹ Surfaces with convex, resilient micro and nano features, such as those created through hydrothermal treatments or biomimetic designs, generally preserve high contact angles (above 150°) and low sliding angles, even after hundreds of abrasion cycles.¹⁶¹ Coatings anchored to hydrophobic nanoparticles and elastomeric matrices can retain or regenerate surface roughness during mechanical deformation, thereby enhancing the abrasion resistance.¹⁷⁹ Dominant failure mechanisms after mechanical stress, such as abrasion, friction wear, sandpaper tests, tape peeling, or impact, in durability assessments in nanocomposite-derived superhydrophobic coatings typically include the loss of surface roughness.¹⁸⁰

According to Gemici *et al.*, the extremely thin (100 nm) and highly porous nature of hydrothermally fabricated nanoparticle-containing films most likely enhanced their scratch resistance compared with films prepared *via* a high-temperature calcination process. For superhydrophobic silica

nanoparticle coatings, their initial WCA was $165^\circ\text{--}170^\circ$ with SA of $\sim 2^\circ$. After scratch testing (equivalent to 50–100 abrasion cycles at 100–200 g load), the WCA decreased to $150^\circ\text{--}155^\circ$ and the SA increased to $5^\circ\text{--}8^\circ$; however, the films retained non-wetting properties due to their porous, resilient structure.¹⁸¹ Jung *et al.* evaluated the mechanical durability of a composite superhydrophobic carbon nanotube coating using epoxy as the matrix.¹⁸² The initial WCA was $\sim 160^\circ$ with the SA of $< 5^\circ$. After cyclic wear tests using atomic force microscopy (100 nN load) and ball-on-flat tribometry, the coating retained superhydrophobicity (WCA $> 150^\circ$, SA $< 10^\circ$), with no significant delamination or loss of adhesion to the substrate. Results indicated that the coating retained its adhesion to the substrate and maintained superhydrophobic properties after undergoing cyclic wear tests, which ranged from 100 nN pressure in atomic force microscopy to 10 mN using a ball-on-flat tribometer.¹⁸

7 Techno-economic aspects and process analysis of coating materials

Techno-economic analysis (TEA) is essential for developing superhydrophobic coating materials, as it assesses their feasibility, practicality, and cost-effectiveness. It analyzes the cost-performance balance, including application and material expenses, alongside performance advantages such as durability, water resistance, and lower maintenance needs.¹⁸³ Superhydrophobic nanocomposites frequently utilize advanced materials and manufacturing processes, which can be costly.¹¹⁰ TEA aids in examining the costs related to raw materials, production, labor, and equipment, providing valuable information on the economic viability of transitioning from laboratory-scale to industrial-scale production (Fig. 10).¹⁸⁴

Zhou *et al.* created hydrophobic anti-icing concrete by incorporating a water-based stone protector and metakaolin. This altered concrete demonstrated outstanding durability, with its de-icing (the process of removing snow, ice or frost from a surface) pressure being approximately 1/16 and 1/22 that of standard concrete and rock, respectively. Additionally, the study confirmed that this material is feasible for large-scale applications in terms of both practicality and cost-effectiveness, making it advantageous for removing ice from tunnel linings and slope rock masses during winter.⁸²

8 Superhydrophobic coatings for the protection of concrete structures: successful case studies

Superhydrophobic coatings fabricated with suitable roughness patterns and low surface energy materials exhibit various functional effects in self-cleaning, anti-fogging, anti-fouling, drag reduction, anti-corrosion, *etc.*¹⁸⁵

Maintaining the exterior surfaces of concrete structures is crucial for preserving their aesthetic appeal and ensuring they remain durable in practical applications. Especially when compared to modern structures, the conservation and restoration of historical buildings made of brick, wood, and natural



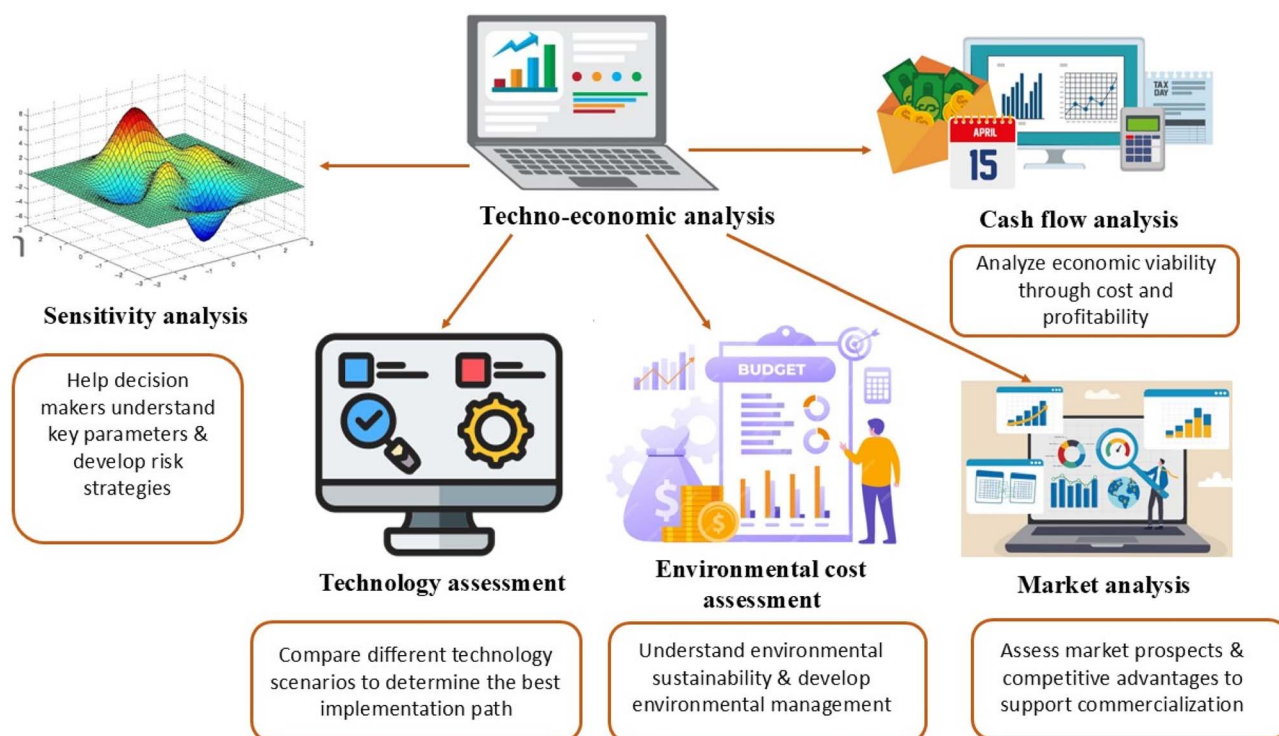


Fig. 10 Techno-economic analysis of coating materials.

stones such as marble is essential.¹⁸⁶ Fig. 11 illustrates how the flexibility of coating formulas based on TiO₂ nanoparticles and other materials provides different substrates with superhydrophobicity and imparts additional practical and functional properties, such as excellent UV resistance.¹⁸⁷ A blend of silica nanoparticles with polyurethane (PU) or epoxy resin can significantly enhance the mechanical durability of superhydrophobic coatings due to their superior adhesion strength to substrates.¹⁸⁸

In another study, Xu *et al.* prepared a hydrophobic coating for cement mortar by adding stearic acid-modified superhydrophobic zeolite powder to reduce the surface energy, which significantly reduced the capillary water absorption of the mortar and improved its anti-erosion properties.¹⁸⁹ Song *et al.* developed a fluorine-free superhydrophobic cement concrete surface coating that exhibited high surface mechanical strength and remained superhydrophobic after multiple scrapings or sandpaper abrasion for 20 m.¹⁹⁰

Aslanidou *et al.* sprayed a mixture of SiO₂ nanoparticles and an emulsion containing silane, siloxane, and organic polymer onto white marble and grey sandstone. This treatment was designed to impart both superoleophobicity and superhydrophobicity properties, helping to keep the surfaces clean and visually appealing.¹⁹¹

9 Technical challenges in commercial production of superhydrophobic coating materials

The scalability and uniformity of superhydrophobic coatings for building applications face significant challenges primarily due

to mechanical durability and low surface energy.¹⁹² The application process itself, whether by spraying, dipping, or brushing, can lead to uneven coverage.¹²⁹ However, maintaining the nanoscale structure required for superhydrophobicity uniformly over a large surface is often cost-prohibitive. Environmental factors such as heavy rainfall, UV exposure, temperature fluctuations, and mechanical abrasion further complicate efforts to ensure long-term uniformity and scalability.¹³¹

9.1 Challenges in scalability

Many fabrication methods involve complex, multi-step processes or expensive materials, making large-scale production economically unviable. Consequently, transitioning from laboratory-scale synthesis to industrial-scale manufacturing often increases costs.¹⁵⁷ The required micro/nanostructure and chemical composition for superhydrophobicity can be difficult to replicate consistently over large areas.¹⁵⁶ The fabrication of superhydrophobic surfaces by techniques such as electrospinning, chemical vapour deposition, and plasma treatments can be effective, but the significant scalability problems are primarily due to the difficulty in maintaining reliable surface roughness and chemical composition over huge areas. Variations in coating thickness, structure, or composition can result in incompatible superhydrophobic performances,¹⁹³ which is compounded by the widespread use of fluorinated compounds in traditional coatings that pose significant environmental hazards.¹⁹⁴ The selection of coatings is largely based on short-term laboratory testing results, with a limited understanding of their long-term performance in real-world environments. For



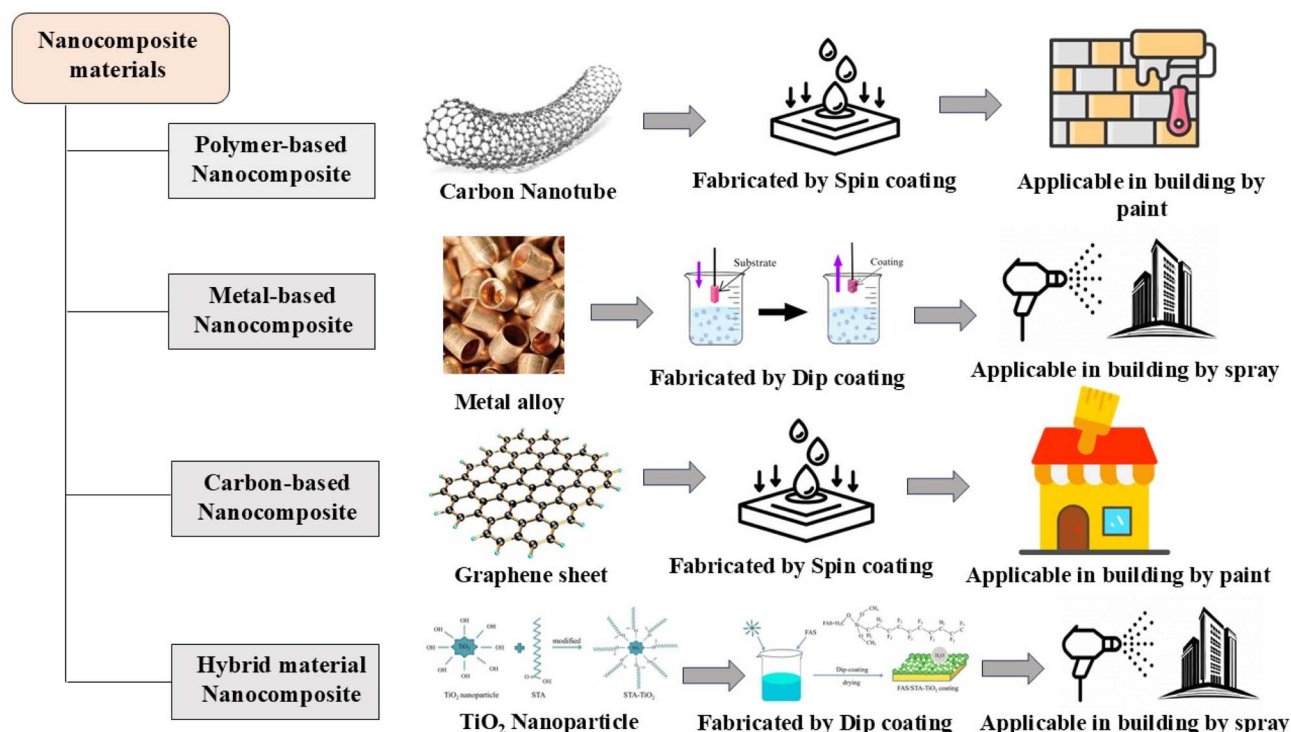


Fig. 11 Application of various nanocomposite materials in concrete structure coatings.

example, while penetrating hydrophobic coatings demonstrate excellent chloride ion resistance in laboratory experiments, their effectiveness on concrete applications may be significantly reduced due to insufficient application thicknesses or improper substrate preparation.¹⁹⁵ Therefore, the development of sustainable and eco-friendly alternatives is essential to support the large-scale implementation of superhydrophobic surfaces.

9.2 Challenges in uniformity

Concrete structure protection materials require uniformity in superhydrophobic coatings, mainly due to the minimal balance required between achieving the appropriate micro- and nano-scale surface structure and ensuring mechanical integrity.¹⁹⁶ Environmental factors such as temperature and humidity during application can impact the coating performance. Mechanical stability issues complicate this problem, where adhesives or elastic materials can create weak points vulnerable to abrasion, UV degradation, or thermal expansion mismatch in outdoor environments.¹³⁴

10 Future perspectives

Next-generation superhydrophobic coatings are being developed to overcome traditional limitations, including poor mechanical strength, accelerated aging, and environmental degradation.¹²⁴ Applying superhydrophobic treatments to coating materials significantly enhances their waterproofing and impermeability, as well as their resistance to chloride ion penetration, freeze-thaw cycles, and other environmental factors. Future developments are likely to focus on

environmentally benign formulations using bio-based polymers, aligning with green building standards and sustainability goals.¹⁵ Furthermore, innovative coatings with embedded nano-sensors could enable real-time monitoring of structural health, allowing for predictive maintenance and prolonging service life.²⁵

10.1 Durability enhancements

A primary emphasis is on extending the lifespan and strength of these coatings. This includes creating materials and methods capable of enduring mechanical abrasion, chemical interactions, and environmental pressures.¹⁹⁷

10.2 Eco-friendly coatings

There is a growing emphasis on replacing traditional fluorinated chemicals with sustainable alternatives, recognized for their environmental damage. Materials and coatings inspired by nature and sourced from biomass are quickly gaining popularity.¹¹⁰

10.3 Scalability and cost reduction

Many advanced manufacturing techniques, including chemical vapor deposition (CVD) or specialized etching methods, can produce high-performance superhydrophobic coatings.⁷⁰ However, these techniques are costly and challenging to scale, restricting the practicality and economic viability of superhydrophobic coatings in commercial settings. Superhydrophobic coatings have a transformative future, with applications that enhance durability, eco-friendliness, and



multi-functionality to make them widely accessible and sustainable.

10.4 Customization and application-specific coatings

Tailored coatings designed for specific building materials and environmental conditions will enhance the performance and foster adoption in diverse architectural contexts.¹³³

11 Conclusion

Next-generation nanocomposite-based superhydrophobic coatings represent a transformative approach to sustainable heritage and concrete structure protection. By combining advanced nanostructured materials with durable, multifunctional properties, these coatings offer exceptional water repellency, self-cleaning capabilities, and resistance to environmental degradation. Their ability to prevent water infiltration, inhibit microbial growth, and reduce surface erosion makes them particularly valuable for preserving cultural heritage while ensuring long-term structural integrity. Despite the challenges associated with large-scale applications, uniformity, and long-term durability, ongoing research is paving the way for the wider application of scalable, eco-friendly, and adaptive coating technologies. Conventional superhydrophobic coatings for concrete often rely on fluorinated compounds (*e.g.*, fluoroalkylsilanes) combined with simple hydrophobic intrusions or basic nanoparticle embeddings. These coatings rely mainly on micro-scale roughness and hydrophobic surfaces to achieve high water contact angles. However, the use of harmful fluorinated materials and their poor mechanochemical stability limit their practical application. In contrast, next-generation nanocomposite-based superhydrophobic coatings emphasize sustainable, eco-friendly, and high-performance innovations, including non-fluorinated modifiers (*e.g.*, stearic acid, polydimethylsiloxane/PDMS or alkyl silanes), bio-based materials (*e.g.*, lignin and cellulose derivatives), and hierarchical micro/nano structures *via* advanced spray or sol-gel methods. It is important to remember that the traditional paint and coating industry has also developed many high-performance coatings that are as durable and effective as solvent-based paints or oil-based paints. Major hydrophobic acrylics and polyurethanes, silicones, waxes, and oils disperse easily in water and can easily coat almost any surface. Most studies have employed different techniques to assess the mechanical durability of superhydrophobic coatings, including sandpaper abrasion, adhesive tape peeling, and finger abrasion, among others. Nevertheless, there is a dearth of standardized methods for evaluating the durability of these coatings. In future works, more attention should be paid to improving durability and developing better durability test methods simulating the real conditions under which superhydrophobic coatings are subjected.

Conflicts of interest

There are no conflicts to declare.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

References

- 1 Y. Zhang, H. Cao, H. Huang and Z. Wang, Hydrophobic Modification of Magnesium Hydroxide Coating Deposited Cathodically on Magnesium Alloy and its Corrosion Protection, *Coatings*, 2019, **9**(8), 477.
- 2 N. L. Othman, M. Jaafar, W. M. W. Harun and F. Ibrahim, A Case Study on Moisture Problems and Building Defects, *Procedia Soc. Behav. Sci.*, 2015, **170**, 27–36.
- 3 Y. Bai, H. Zhang, Y. Shao, H. Zhang and J. Zhu, Recent Progresses of Superhydrophobic Coatings in Different Application Fields: An Overview, *Coatings*, 2021, **11**(2), 116.
- 4 E. A. R. De Campos, R. N. Pagani, L. M. Resende and J. Pontes, Construction and qualitative assessment of a bibliographic portfolio using the methodology Methodi Ordinatio, *Scientometrics*, 2018, **116**(2), 815–842.
- 5 I. Passas, Bibliometric Analysis: The Main Steps, *Encyclopedia*, 2024, **4**(2), 1014–1025.
- 6 Y. Wang, P. Li, H. Liu, W. Wang, Y. Guo and L. Wang, The Effect of Microbiologically Induced Concrete Corrosion in Sewer on the Bearing Capacity of Reinforced Concrete Pipes: Full-Scale Experimental Investigation, *Buildings*, 2022, **12**(11), 1996.
- 7 X. Wu, F. Chu, D. Orejon and T. Mouterde, Superhydrophobic surfaces: Fundamentals, manufacture, and applications, *Appl. Phys. Lett.*, 2024, **124**(2), 020401.
- 8 L. Guo, L. Wang, X. Zhao and M. Peng, Non-whitening superhydrophobic coating for heritage protection, *Colloids Surf., A*, 2023, **676**, 132294.
- 9 P. H. C. Camargo, K. G. Satyanarayana and F. Wypych, Nanocomposites: synthesis, structure, properties and new application opportunities, *Mater. Res.*, 2009, **12**(1), 1–39.
- 10 G. Armstrong, An introduction to polymer nanocomposites, *Eur. J. Phys.*, 2015, **36**(6), 063001.
- 11 D. R. Paul and L. M. Robeson, Polymer nanotechnology: Nanocomposites, *Polymer*, 2008, **49**(15), 3187–3204.
- 12 E. Onyinye Nwulu, T. Y. Elete, F. E. Adikwu and F. O. Onyeke, Advancing inspection techniques for coating durability: A framework for integrating non-destructive testing technologies, *Int. J. Sci. Res. Updat.*, 2024, **8**(2), 164–174.
- 13 V. E. Ovie, C. Nwakile, O. A. Akano, A. T. Aderamo and E. Hanson, Advanced maintenance strategies for energy infrastructure: Lessons for optimizing rotating machinery, *Glob. J. Sci. Res.*, 2024, **2**(2), 065–093.
- 14 O. Ayotunde Akano, E. Hanson, C. Nwakile and A. E. Esiri, Designing real-time safety monitoring dashboards for industrial operations: A data-driven approach, *Glob. J. Sci. Res.*, 2024, **2**(2), 001–009.
- 15 G. Liao, W. Yao, A. She and X. Bian, An eco-friendly building coating with high self-cleaning capacity: Synergetic effect of



- super-hydrophobicity and photocatalytic degradation, *Constr. Build. Mater.*, 2023, **406**, 133406.
- 16 S. S. Ray, P. R. T. Peddinti, R. Soni, B. Kim, Y. I. Park, I. C. Kim, *et al.*, Effectiveness of nanoparticles-based ultrahydrophobic coating for concrete materials, *J. Build. Eng.*, 2023, **66**, 105799.
 - 17 P. R. T. Peddinti, H. Puppala, B. Kim, S. Karmakar, V. Syed, R. Selvasembian, *et al.*, Durable hydrophobic multifunctional nanocoating for long-term protection of stone built heritage, *Colloids Surf., A*, 2026, **729**, 138895.
 - 18 Y. C. Jung and B. Bhushan, Mechanically Durable Carbon Nanotube–Composite Hierarchical Structures with Superhydrophobicity, Self-Cleaning, and Low-Drag, *ACS Nano*, 2009, **3**(12), 4155–4163.
 - 19 R. Soni, Y. T. Kim, A. Aabloo, C. Bathula, H. S. Kim, S. S. Ray, *et al.*, Scalable and Durable Superhydrophobic Coating Using Shellac-Based Bioadhesive and Hierarchical Silica Nanoparticles, *Langmuir*, 2025, **41**(5), 3269–3277.
 - 20 S. S. Ray, R. Soni, I. C. Kim, Y. I. Park, C. Y. Lee and Y. N. Kwon, Surface innovation for fabrication of superhydrophobic sand grains with improved water holding capacity for various environmental applications, *Environ. Technol. Innovation*, 2022, **28**, 102849.
 - 21 S. Sinha Ray, H. K. Lee, D. T. T. Huyen, Y. I. Park, H. Park, S. E. Nam, *et al.*, Fluorine-free anti-droplet surface modification by hexadecyltrimethoxysilane-modified silica nanoparticles-coated carbon nanofibers for self-cleaning applications, *Prog. Org. Coat.*, 2021, **153**, 106165.
 - 22 J. T. Simpson, S. R. Hunter and T. Aytug, Superhydrophobic materials and coatings: a review, *Rep. Prog. Phys.*, 2015, **78**(8), 086501.
 - 23 I. S. Bayer, Superhydrophobic Coatings from Ecofriendly Materials and Processes: A Review, *Adv. Mater. Interfaces*, 2020, **7**(13), 2000095.
 - 24 H. Y. Erbil and C. E. Cansoy, Range of Applicability of the Wenzel and Cassie–Baxter Equations for Superhydrophobic Surfaces, *Langmuir*, 2009, **25**(24), 14135–14145.
 - 25 Y. Cao, A. Salvini and M. Camaiti, Current Status and Future Prospects of Applying Bioinspired Superhydrophobic Materials for Conservation of Stone Artworks, *Coatings*, 2020, **10**(4), 353.
 - 26 T. Xiang, Z. Lv, F. Wei, J. Liu, W. Dong, C. Li, *et al.*, Superhydrophobic Civil Engineering Materials: A Review from Recent Developments, *Coatings*, 2019, **9**(11), 753.
 - 27 A. M. A. Mohamed, A. M. Abdullah and N. A. Younan, Corrosion behavior of superhydrophobic surfaces: A review, *Arabian J. Chem.*, 2015, **8**(6), 749–765.
 - 28 D. Gh Barati, M. Aliofkhazraei, S. Khorsand, S. Sokhanvar and A. Kaboli, Science and Engineering of Superhydrophobic Surfaces: Review of Corrosion Resistance, Chemical and Mechanical Stability, *Arabian J. Chem.*, 2020, **13**(1), 1763–1802.
 - 29 N. Rungruangkitkrai, P. Phromphen, N. Chartvivatpornchai, A. Srisa, Y. Laorenza, P. Wongphan, *et al.*, Water Repellent Coating in Textile, Paper and Bioplastic Polymers: A Comprehensive Review, *Polymers*, 2024, **16**(19), 2790.
 - 30 A. J. Haider, Z. N. Jameel and I. H. M. Al-Hussaini, Review on: Titanium Dioxide Applications, *Energy Procedia*, 2019, **157**, 17–29.
 - 31 A. Syafiq, B. Vengadaesvaran, U. Ahmed, N. A. Rahim, A. K. Pandey, A. R. Bushroa, *et al.*, Facile synthesise of transparent hydrophobic nano-CaCO₃ based coatings for self-cleaning and anti-fogging, *Mater. Chem. Phys.*, 2020, **239**, 121913.
 - 32 S. Silviana, A. Darmawan, F. Dalanta, A. Subagio, F. Hermawan and H. Milen Santoso, Superhydrophobic Coating Derived from Geothermal Silica to Enhance Material Durability of Bamboo Using Hexadimethylsilazane (HMDS) and Trimethylchlorosilane (TMCS), *Materials*, 2021, **14**(3), 530.
 - 33 M. Ghashghae, M. Fallah and A. Rabiee, Superhydrophobic nanocomposite coatings of poly(methyl methacrylate) and stearic acid grafted CuO nanoparticles with photocatalytic activity, *Prog. Org. Coat.*, 2019, **136**, 105270.
 - 34 A. Kurbanova, N. Myrzakhmetova, N. Akimbayeva, K. Kishibayev, M. Nurbekova, Y. Kanagat, *et al.*, Superhydrophobic SiO₂/Trimethylchlorosilane Coating for Self-Cleaning Application of Construction Materials, *Coatings*, 2022, **12**(10), 1422.
 - 35 M. Zainuri, W. Dini Putri and A. S. Bintoro, Hydrophobicity of tetraethyl-orthosilicate-derived silica coating at various concentrations, *J. Phys.:Conf. Ser.*, 2021, **1951**(1), 012021.
 - 36 S. K. Kirthika, G. Goel, A. Matthews and S. Goel, Review of the untapped potentials of antimicrobial materials in the construction sector, *Prog. Mater. Sci.*, 2023, **133**, 101065.
 - 37 R. Teixeira-Santos, M. Gomes, L. C. Gomes and F. J. Mergulhão, Antimicrobial and anti-adhesive properties of carbon nanotube-based surfaces for medical applications: a systematic review, *iScience*, 2021, **24**(1), 102001.
 - 38 R. U. D. Nassar, P. Soroushian, T. Ghebrab and M. Sufyan-Ud-Din, Development and evaluation of mixture formulations to enhance concrete resistance to microbial-induced corrosion, *Results Mater.*, 2024, **24**, 100644.
 - 39 L. Kong, Z. Zhang, H. Jiao, Y. Liu and H. Yang, Effect of hydrophobic modification on the anti-microbial induced corrosion of alkali-activated mortar, *Constr. Build. Mater.*, 2025, **458**, 139576.
 - 40 A. Reffae, M. Saied, S. F. Hamieda and ShK. Amin, Fabrication of green anti-microbial and anti-static cement building bricks, *Sci. Rep.*, 2024, **14**(1), 6313.
 - 41 H. Zhang, P. Tang, Y. Tang, K. Yang and Q. Wang, MXene-Functionalized Light-Induced Antimicrobial and Waterproof Polyacrylate Coating for Cementitious Materials Protection, *Polymers*, 2023, **15**(9), 2076.
 - 42 K. S. Huang, C. H. Yang, S. L. Huang, C. Y. Chen, Y. Y. Lu and Y. S. Lin, Recent Advances in Antimicrobial Polymers: A Mini-Review, *Int. J. Mol. Sci.*, 2016, **17**(9), 1578.
 - 43 J. A. D. Olmo, L. Ruiz-Rubio, L. Pérez-Alvarez, V. Sáez-Martínez and J. L. Vilas-Vilela, Antibacterial Coatings for



- Improving the Performance of Biomaterials, *Coatings*, 2020, **10**(2), 139.
- 44 M. T. Marvila, A. R. G. Azevedo, D. Cecchin, J. M. Costa, G. C. Xavier, D. De Fátima Do Carmo, *et al.*, Durability of coating mortars containing açai fibers, *Case Stud. Constr. Mater.*, 2020, **13**, e00406.
- 45 S. K. Kaliyavaradhan and T. C. Ling, Potential of CO₂ sequestration through construction and demolition (C&D) waste—An overview, *J. CO₂ Util.*, 2017, **20**, 234–242.
- 46 R. Kumar, A. Umar, G. Kumar and H. S. Nalwa, Antimicrobial properties of ZnO nanomaterials: A review, *Ceram. Int.*, 2017, **43**(5), 3940–3961.
- 47 Y. Su, K. Wang, J. Gao, Y. Yang, Y. X. Qin, Y. Zheng, *et al.*, Enhanced cytocompatibility and antibacterial property of zinc phosphate coating on biodegradable zinc materials, *Acta Biomater.*, 2019, **98**, 174–185.
- 48 S. A. Ruffolo and M. F. La Russa, Nanostructured Coatings for Stone Protection: An Overview, *Front Mater.*, 2019, **6**, 147.
- 49 F. Yang, W. Zhou, F. Li, L. Yuan, Y. Diao, Y. Liu, *et al.*, Sprayable coating based on fluorinated silica nanocomposites with superhydrophobic and antibacterial properties for advanced concrete, *Prog. Nat. Sci.:Mater. Int.*, 2022, **32**(4), 472–481.
- 50 J. Becerra, A. P. Zaderenko, M. J. Sayagués, R. Ortiz and P. Ortiz, Synergy achieved in silver-TiO₂ nanocomposites for the inhibition of biofouling on limestone, *Build. Environ.*, 2018, **141**, 80–90.
- 51 V. Vishwakarma, U. Sudha, D. Ramachandran, B. Anandkumar, R. P. George, K. Kumari, *et al.*, Enhancing antimicrobial properties of fly ash mortars specimens through nanophase modification, *Mater. Today: Proc.*, 2016, **3**(6), 1389–1397.
- 52 C. Peng, X. Hu, Z. You, F. Xu, G. Jiang, H. Ouyang, *et al.*, Investigation of anti-icing, anti-skid, and water impermeability performances of an acrylic superhydrophobic coating on asphalt pavement, *Constr. Build. Mater.*, 2020, **264**, 120702.
- 53 R. Di Mundo, C. Labianca, G. Carbone and M. Notarnicola, Recent Advances in Hydrophobic and Icephobic Surface Treatments of Concrete, *Coatings*, 2020, **10**(5), 449.
- 54 W. She, J. Yang, J. Hong, D. Sun, S. Mu and C. Miao, Superhydrophobic concrete with enhanced mechanical robustness: Nanohybrid composites, strengthen mechanism and durability evaluation, *Constr. Build. Mater.*, 2020, **247**, 118563.
- 55 C. Dong, N. Shao, F. Yan, R. Ji, X. Wei and Z. Zhang, A novel integration strategy for the foaming and hydrophobization of geopolymer foams, *Cem. Concr. Res.*, 2022, **160**, 106919.
- 56 D. Shi, Y. Geng, S. Li, J. Gao, D. Hou, Z. Jin, *et al.*, Efficacy and mechanism of graphene oxide modified silane emulsions on waterproof performance of foamed concrete, *Case Stud. Constr. Mater.*, 2022, **16**, e00908.
- 57 Z. Lu, J. Chen and X. Zhang, Superhydrophobic Coating Deposited on Foamed Concrete with Super-Robust Mechanical and Self-Repairing Properties, *Phys. Status Solidi A*, 2022, **219**(24), 2200417.
- 58 I. Karapanagiotis, P. N. Manoudis, A. Zurba and D. Lampakis, From Hydrophobic to Superhydrophobic and Superhydrophilic Siloxanes by Thermal Treatment, *Langmuir*, 2014, **30**(44), 13235–13243.
- 59 S. Huang, G. Liu, K. Zhang, H. Hu, J. Wang, L. Miao, *et al.*, Water-based polyurethane formulations for robust superhydrophobic fabrics, *Chem.-Eng. J.*, 2019, **360**, 445–451.
- 60 A. M. Atta, M. H. El-Newehy, M. M. Abdulhameed, M. H. Wahby and A. I. Hashem, Seawater Absorption and Adhesion Properties of Hydrophobic and Superhydrophobic Thermoset Epoxy Nanocomposite Coatings, *Nanomaterials*, 2021, **11**(2), 272.
- 61 M. Yu, P. Li, Y. Feng, Q. Li, W. Sun, M. Quan, *et al.*, Positive effect of polymeric silane-based water repellent agents on the durability of superhydrophobic fabrics, *Appl. Surf. Sci.*, 2018, **450**, 492–501.
- 62 P. He, J. Qu, S. Li, R. Sun, K. Huang, J. Zhao, *et al.*, Study on the construction of durable superhydrophobic coatings using simple spray coating method and their underwater drag reduction performance, *Colloids Surf., A*, 2024, **701**, 134858.
- 63 Q. Xiao, Coating and Film-Forming Properties. in *Food Hydrocolloids: Functionalities and Applications*, ed. Fang Y., Zhang H. and Nishinari K., Singapore, Springer, 2021, pp. 267–306, DOI: [10.1007/978-981-16-0320-4_8](https://doi.org/10.1007/978-981-16-0320-4_8).
- 64 Y. Wang and X. Gong, Special oleophobic and hydrophilic surfaces: approaches, mechanisms, and applications, *J. Mater. Chem. A*, 2017, **5**(8), 3759–3773.
- 65 C. Peng, Z. Chen and M. K. Tiwari, All-organic superhydrophobic coatings with mechanochemical robustness and liquid impalement resistance, *Nat. Mater.*, 2018, **17**(4), 355–360.
- 66 A. M. C. Maan, A. H. Hofman, W. M. De Vos and M. Kamperman, Recent Developments and Practical Feasibility of Polymer-Based Antifouling Coatings, *Adv. Funct. Mater.*, 2020, **30**(32), 2000936.
- 67 S. Gupta, A. Babu, H. S. Arora and H. S. Grewal, High durability of non-fluorinated superhydrophobic nanocomposite coatings, *Mater. Lett.*, 2020, **270**, 127717.
- 68 R. S. Sutar, S. S. Gaikwad, S. S. Latthe, V. S. Kodag, S. B. Deshmukh, L. P. Saptal, *et al.*, Superhydrophobic Nanocomposite Coatings of Hydrophobic Silica NPs and Poly(methyl methacrylate) with Notable Self-Cleaning Ability, *Macromol. Symp.*, 2020, **393**(1), 2000116.
- 69 S. Wang, Y. Wang, Y. Zou, G. Chen, J. Ouyang, D. Jia, *et al.*, Scalable-Manufactured Superhydrophobic Multilayer Nanocomposite Coating with Mechanochemical Robustness and High-Temperature Endurance, *ACS Appl. Mater. Interfaces*, 2020, **12**(31), 35502–35512.
- 70 D. Veeman, M. V. Shree, P. Sureshkumar, T. Jagadeesha, L. Natrayan, M. Ravichandran, *et al.*, Sustainable Development of Carbon Nanocomposites: Synthesis and Classification for Environmental Remediation, *J. Nanomater.*, 2021, **2021**, 1–21.
- 71 P. Nguyen-Tri, T. A. Nguyen, P. Carriere and C. Ngo Xuan, Nanocomposite Coatings: Preparation, Characterization,



- Properties, and Applications, *Int. J. Corros.*, 2018, **2018**, 1–19.
- 72 I. O. Arukalam, E. E. Oguzie and Y. Li, Nanostructured superhydrophobic polysiloxane coating for high barrier and anticorrosion applications in marine environment, *J. Colloid Interface Sci.*, 2018, **512**, 674–685.
- 73 S. Ahmad, W. A. Siddiqi and S. Ahmad, Sustainable nanocomposite porous absorbent and membrane sieves: Definition, classification, history, properties, synthesis, applications, and future prospects, *J. Environ. Chem. Eng.*, 2023, **11**(2), 109367.
- 74 N. G. Sahoo, S. Rana, J. W. Cho, L. Li and S. H. Chan, Polymer nanocomposites based on functionalized carbon nanotubes, *Prog. Polym. Sci.*, 2010, **35**(7), 837–867.
- 75 K. Qi, Y. Sun, H. Duan and X. Guo, A corrosion-protective coating based on a solution-processable polymer-grafted graphene oxide nanocomposite, *Corros. Sci.*, 2015, **98**, 500–506.
- 76 L. Peponi, D. Puglia, L. Torre, L. Valentini and J. M. Kenny, Processing of nanostructured polymers and advanced polymeric based nanocomposites, *Mater. Sci. Eng., R*, 2014, **85**, 1–46.
- 77 J. Silvestre, N. Silvestre and J. De Brito, Polymer nanocomposites for structural applications: Recent trends and new perspectives, *Mech. Adv. Mater. Struct.*, 2016, **23**(11), 1263–1277.
- 78 S. Amiri and A. Rahimi, Synthesis and characterization of supramolecular corrosion inhibitor nanocontainers for anticorrosion hybrid nanocomposite coatings, *J. Polym. Res.*, 2015, **22**(5), 66.
- 79 R. Woo, H. Zhu, M. Chow, C. Leung and J. Kim, Barrier performance of silane–clay nanocomposite coatings on concrete structure, *Compos. Sci. Technol.*, 2008, **68**(14), 2828–2836.
- 80 J. Tang, D. Chen, Q. Yao, J. Xie and J. Yang, Recent advances in noble metal-based nanocomposites for electrochemical reactions, *Mater. Today Energy*, 2017, **6**, 115–127.
- 81 J. Abdi, M. Vossoughi, N. M. Mahmoodi and I. Alemzadeh, Synthesis of metal-organic framework hybrid nanocomposites based on GO and CNT with high adsorption capacity for dye removal, *Chem. Eng. J.*, 2017, **326**, 1145–1158.
- 82 L. Zhou, X. Zhang, L. Ma, J. Gao and Y. Jiang, Acetylcholinesterase/chitosan-transition metal carbides nanocomposites-based biosensor for the organophosphate pesticides detection, *Biochem. Eng. J.*, 2017, **128**, 243–249.
- 83 L. Ceschini, A. Dahle, M. Gupta, A. E. W. Jarfors, S. Jayalakshmi and A. Morri, *et al.*, Ex Situ Production Routes for Metal Matrix Nanocomposites, in *Aluminum and Magnesium Metal Matrix Nanocomposites*, Springer, Singapore, 2017, pp. 19–40, DOI: [10.1007/978-981-10-2681-2_2](https://doi.org/10.1007/978-981-10-2681-2_2).
- 84 I. Ahmad, U. Khan and Y. K. Gun'ko, Graphene, carbon nanotube and ionic liquid mixtures: towards new quasi-solid state electrolytes for dye sensitised solar cells, *J. Mater. Chem.*, 2011, **21**(42), 16990.
- 85 M. S. Mauter and M. Elimelech, Environmental Applications of Carbon-Based Nanomaterials, *Environ. Sci. Technol.*, 2008, **42**(16), 5843–5859.
- 86 K. Scida, P. W. Stege, G. Haby, G. A. Messina and C. D. García, Recent applications of carbon-based nanomaterials in analytical chemistry: Critical review, *Anal. Chim. Acta*, 2011, **691**(1–2), 6–17.
- 87 M. M. Ghafurian, H. Niazmand, F. T. Dastjerd and O. Mahian, A study on the potential of carbon-based nanomaterials for enhancement of evaporation and water production, *Chem. Eng. Sci.*, 2019, **207**, 79–90.
- 88 A. Yadav, R. Kumar and B. Sahoo, Graphene Oxide Coatings on Amino Acid Modified Fe Surfaces for Corrosion Inhibition, *ACS Appl. Nano Mater.*, 2020, **3**(4), 3540–3557.
- 89 G. Awasthi, R. Sharma, S. Sundarrajan, S. Ramakrishna and P. Kumar, Progressive Trends in Hybrid Material-Based Chemiresistive Sensors for Nitroaromatic Compounds, *Polymers*, 2022, **14**(21), 4643.
- 90 A. Boualem, A. Yahiaoui and A. Dehbi, Synthesis and Characterization of Hybrid Material Based on Poly(pyrrole-co-N-methyl pyrrole) and ZnCo2O4, *Polym. Sci., Ser. B*, 2020, **62**(6), 750–755.
- 91 R. D'Amato, L. Caneve, C. Giancristofaro, F. Persia, L. Pilloni and A. Rinaldi, Development of nanocomposites for conservation of artistic stones, *Proc. Inst. Mech. Eng., Part N*, 2014, **228**(1), 19–26.
- 92 M. M. Abolghasemi, V. Yousefi and B. Hazizadeh, An inorganic–organic hybrid material based on ZnO nanoparticles anchored to a composite made from polythiophene and hexagonally ordered silica for use in solid-phase fiber microextraction of PAHs, *Microchim. Acta*, 2014, **181**(5–6), 639–645.
- 93 I. Khan, K. Saeed and I. Khan, Nanoparticles: Properties, applications and toxicities, *Arabian J. Chem.*, 2019, **12**(7), 908–931.
- 94 C. Esposito Corcione, N. De Simone, M. L. Santarelli and M. Frigione, Protective properties and durability characteristics of experimental and commercial organic coatings for the preservation of porous stone, *Prog. Org. Coat.*, 2017, **103**, 193–203.
- 95 J. Shen, J. Liang, X. Lin, H. Lin, J. Yu and Z. Yang, Recent Progress in Polymer-Based Building Materials, *Int. J. Polym. Sci.*, 2020, 1–15.
- 96 T. Martinez, A. Bertron, G. Escadeillas, E. Ringot and V. Simon, BTEX abatement by photocatalytic TiO₂-bearing coatings applied to cement mortars, *Build. Environ.*, 2014, **71**, 186–192.
- 97 W. Gu, R. Liu, Y. Zhang, X. Yu, P. Feng, Q. Ran, *et al.*, Robust water-borne multi-layered superhydrophobic coating on concrete with ultra-low permeability, *Constr. Build. Mater.*, 2024, **411**, 134573.
- 98 A. H. Alateah, Graphene concrete: Recent advances in production methods, performance properties, environmental impact and economic viability, *Case Stud. Constr. Mater.*, 2023, **19**, e02653.
- 99 A. A. Shirzadi Javid, P. Ghoddousi, M. Zareechian and A. Habibnejad Korayem, Effects of Spraying Various



- Nanoparticles at Early Ages on Improving Surface Characteristics of Concrete Pavements, *Int. J. Civ. Eng.*, 2019, **17**(9), 1455–1468.
- 100 A. Habibnejad Korayem, P. Ghoddousi, A. A. Shirzadi Javid, M. A. Oraie and H. Ashegh, Graphene oxide for surface treatment of concrete: A novel method to protect concrete, *Constr. Build. Mater.*, 2020, **243**, 118229.
- 101 K. Gong, Z. Pan, A. H. Korayem, L. Qiu, D. Li, F. Collins, *et al.*, Reinforcing Effects of Graphene Oxide on Portland Cement Paste, *J. Mater. Civ. Eng.*, 2015, **27**(2), A4014010.
- 102 Z. Pan, L. He, L. Qiu, A. H. Korayem, G. Li, J. W. Zhu, *et al.*, Mechanical properties and microstructure of a graphene oxide–cement composite, *Cem. Concr. Compos.*, 2015, **58**, 140–147.
- 103 X. Li, A. H. Korayem, C. Li, Y. Liu, H. He, J. G. Sanjayan, *et al.*, Incorporation of graphene oxide and silica fume into cement paste: A study of dispersion and compressive strength, *Constr. Build. Mater.*, 2016, **123**, 327–335.
- 104 M. H. Marey, An effective polymer nanocomposite based on tetraethoxysilane (TEOS) and SiO₂-Al₂O₃ nanoparticles for super protection of damaged ancient Egyptian wall paintings, *Pigm. Resin Technol.*, 2022, **51**(3), 344–353.
- 105 N. Cohen, A. Dotan, H. Dodiuk and S. Kenig, Superhydrophobic Coatings and Their Durability, *Mater. Manuf. Processes*, 2016, **31**(9), 1143–1155.
- 106 J. Radnik, R. Kersting, B. Hagenhoff, F. Bennet, D. Ciornii, P. Nymark, *et al.*, Reliable Surface Analysis Data of Nanomaterials in Support of Risk Assessment Based on Minimum Information Requirements, *Nanomaterials*, 2021, **11**(3), 639.
- 107 D. Bokov, A. Turki Jalil, S. Chupradit, W. Suksatan, M. Javed Ansari, I. H. Shewael, *et al.*, Nanomaterial by Sol-Gel Method: Synthesis and Application, *Adv. Mater. Sci. Eng.*, 2021, **2021**(1), 5102014.
- 108 D. R. Baer, M. H. Engelhard, G. E. Johnson, J. Laskin, J. Lai, K. Mueller, *et al.*, Surface characterization of nanomaterials and nanoparticles: Important needs and challenging opportunities, *J. Vac. Sci. Technol., A*, 2013, **31**(5), 050820.
- 109 R. Ramachandran, M. Kozhukhova, K. Sobolev and M. Nosonovsky, Anti-Icing Superhydrophobic Surfaces: Controlling Entropic Molecular Interactions to Design Novel Icephobic Concrete, *Entropy*, 2016, **18**(4), 132.
- 110 J. Zhao, X. Gao, S. Chen, H. Lin, Z. Li and X. Lin, Hydrophobic or superhydrophobic modification of cement-based materials: A systematic review, *Composites, Part B*, 2022, **243**, 110104.
- 111 W. She, X. Wang, C. Miao, Q. Zhang, Y. Zhang, J. Yang, *et al.*, Biomimetic superhydrophobic surface of concrete: Topographic and chemical modification assembly by direct spray, *Constr. Build. Mater.*, 2018, **181**, 347–357.
- 112 S. S. Latthe, R. S. Sutar, V. S. Kodag, A. K. Bhosale, A. M. Kumar, K. Kumar Sadasivuni, *et al.*, Self – cleaning superhydrophobic coatings: Potential industrial applications, *Prog. Org. Coat.*, 2019, **128**, 52–58.
- 113 Y. Liao, C. H. Loh, M. Tian, R. Wang and A. G. Fane, Progress in electrospun polymeric nanofibrous membranes for water treatment: Fabrication, modification and applications, *Prog. Polym. Sci.*, 2018, **77**, 69–94.
- 114 F. Zhang, H. Qian, L. Wang, Z. Wang, C. Du, X. Li, *et al.*, Superhydrophobic carbon nanotubes/epoxy nanocomposite coating by facile one-step spraying, *Surf. Coat. Technol.*, 2018, **341**, 15–23.
- 115 L. Q. Xu, K. G. Neoh and E. T. Kang, Natural polyphenols as versatile platforms for material engineering and surface functionalization, *Prog. Polym. Sci.*, 2018, **87**, 165–196.
- 116 A. Asthana, T. Maitra, R. Büchel, M. K. Tiwari and D. Poulikakos, Multifunctional Superhydrophobic Polymer/Carbon Nanocomposites: Graphene, Carbon Nanotubes, or Carbon Black?, *ACS Appl. Mater. Interfaces*, 2014, **6**(11), 8859–8867.
- 117 M. Salehi, M. Mozammel and S. M. Emarati, Superhydrophobic and corrosion resistant properties of electrodeposited Ni-TiO₂/TMPSi nanocomposite coating, *Colloids Surf., A*, 2019, **573**, 196–204.
- 118 R. A. Bahgat, A. Abdullah, A. Mohamed and M. Al-Maadeed, New Electrospun Polystyrene/Al₂O₃ Nanocomposite Superhydrophobic Coatings; Synthesis, Characterization, and Application, *Coatings*, 2018, **8**(2), 65.
- 119 D. G. Papageorgiou, I. A. Kinloch and R. J. Young, Mechanical properties of graphene and graphene-based nanocomposites, *Prog. Mater. Sci.*, 2017, **90**, 75–127.
- 120 M. S. Safavi and A. Rasooli, Ni-P-TiO₂ nanocomposite coatings with uniformly dispersed Ni₃ Ti intermetallics: effects of TiO₂ nanoparticles concentration, *Surf. Eng.*, 2019, **35**(12), 1070–1080.
- 121 H. Fattahimoghaddam, I. H. Kim, K. Dhandapani, Y. J. Jeong and T. K. An, Copper-Nanoparticle-Decorated Hydrothermal Carbonaceous Carbon–Polydimethylsiloxane Nanocomposites: Unveiling Potential in Simultaneous Light-Driven Interfacial Water Evaporation and Power Generation, *Small*, 2024, **20**(37), 2403565.
- 122 Y. Liu, S. Li, J. Zhang, Y. Wang, Z. Han and L. Ren, Fabrication of biomimetic superhydrophobic surface with controlled adhesion by electrodeposition, *Chem.–Eng. J.*, 2014, **248**, 440–447.
- 123 S. J. Hong, F. M. Chang, T. H. Chou, S. H. Chan, Y. J. Sheng and H. K. Tsao, Anomalous Contact Angle Hysteresis of a Captive Bubble: Advancing Contact Line Pinning, *Langmuir*, 2011, **27**(11), 6890–6896.
- 124 V. Soulios, E. Jan De Place Hansen, R. Peuhkuri, E. Møller and A. Ghanbari-Siahkali, Durability of the hydrophobic treatment on brick and mortar, *Build. Environ.*, 2021, **201**, 107994.
- 125 S. Mohammadshahi, J. Breveleri and H. Ling, Fabrication and characterization of super-hydrophobic surfaces based on sandpapers and nano-particle coatings, *Colloids Surf., A*, 2023, **666**, 131358.
- 126 M. Haji-Savameri, A. Irannejad, S. Norouzi-Apourvari, M. Schaffie and A. Hemmati-Sarapardeh, Evaluation of corrosion performance of superhydrophobic PTFE and nanosilica coatings, *Sci. Rep.*, 2022, **12**(1), 17059.



- 127 F. Wang, X. Zhu, H. Liu, S. Lei and D. Huang, Influence of Superhydrophobic Coating on the Water Resistance of Foundry Dust/Magnesium Oxide Cement Composite, *Materials*, 2020, **13**(15), 3431.
- 128 Y. Wu, L. Dong, X. Shu, Y. Yang, W. She and Q. Ran, A review on recent advances in the fabrication and evaluation of superhydrophobic concrete, *Composites, Part B*, 2022, **237**, 109867.
- 129 K. Manoharan and S. Bhattacharya, Superhydrophobic surfaces review: Functional application, fabrication techniques and limitations, *J. Micromanuf.*, 2019, **2**(1), 59–78.
- 130 A. Kumar and D. Nanda, Methods and fabrication techniques of superhydrophobic surfaces, *Superhydrophobic Polymer Coatings*, Elsevier, 2019, pp. 43–75, <https://linkinghub.elsevier.com/retrieve/pii/B9780128166710000047>.
- 131 B. N. Sahoo and B. Kandasubramanian, Recent progress in fabrication and characterisation of hierarchical biomimetic superhydrophobic structures, *RSC Adv.*, 2014, **4**(42), 22053.
- 132 X. Pan, Z. Shi, C. Shi, T. C. Ling and N. Li, A review on concrete surface treatment Part I: Types and mechanisms, *Constr. Build. Mater.*, 2017, **132**, 578–590.
- 133 W. Sun, L. Wang, Z. Yang, S. Li, T. Wu and G. Liu, Fabrication of polydimethylsiloxane-derived superhydrophobic surface on aluminium *via* chemical vapour deposition technique for corrosion protection, *Corros. Sci.*, 2017, **128**, 176–185.
- 134 L. Jiang, J. Yang, C. Wu, X. Wang, J. Feng, R. Zhang, *et al.*, Fabrication of a robust superhydrophobic coating exhibiting superior corrosion resistance *via* spray application technique, *Colloids Surf., A*, 2024, **687**, 133497.
- 135 B. Fotovvati, N. Namdari and A. Dehghanhadikolaei, On Coating Techniques for Surface Protection: A Review, *J. Manuf. Mater. Process.*, 2019, **3**(1), 28.
- 136 F. Wang, H. Liu, J. Ou and W. Li, Fast fabrication of superhydrophobic surfaces on hardened cement paste using sodium laurate aqueous solution, *Constr. Build. Mater.*, 2021, **278**, 122385.
- 137 G. T. Lim, J. E. Puskas, D. H. Reneker, A. Jáklí and W. E. Horton, Highly Hydrophobic Electrospun Fiber Mats from Polyisobutylene-Based Thermoplastic Elastomers, *Biomacromolecules*, 2011, **12**(5), 1795–1799.
- 138 B. Grignard, A. Vaillant, J. De Coninck, M. Piens, A. M. Jonas, C. Detrembleur, *et al.*, Electrospinning of a Functional Perfluorinated Block Copolymer as a Powerful Route for Imparting Superhydrophobicity and Corrosion Resistance to Aluminum Substrates, *Langmuir*, 2011, **27**(1), 335–342.
- 139 D. Zhi, Y. Lu, S. Sathasivam, I. P. Parkin and X. Zhang, Large-scale fabrication of translucent and repairable superhydrophobic spray coatings with remarkable mechanical, chemical durability and UV resistance, *J. Mater. Chem. A*, 2017, **5**(21), 10622–10631.
- 140 Y. Hao, D. M. Soolaman and H. Z. Yu, Controlled Wetting on Electrodeposited Oxide Thin Films: From Hydrophilic to Superhydrophobic, *J. Phys. Chem. C*, 2013, **117**(15), 7736–7743.
- 141 Y. Gao, Y. Sun and D. Guo, Facile fabrication of superhydrophobic surfaces with low roughness on Ti–6Al–4V substrates *via* anodization, *Appl. Surf. Sci.*, 2014, **314**, 754–759.
- 142 G. Huang, Y. Guo, B. Lee, H. Chen and A. Mao, Research Advances and Future Perspectives of Superhydrophobic Coatings in Sports Equipment Applications, *Molecules*, 2025, **30**(3), 644.
- 143 M. Cannio, D. N. Boccaccini, S. Caporali and R. Taurino, Superhydrophobic Materials from Waste: Innovative Approach, *Clean Technol.*, 2024, **6**(1), 299–321.
- 144 E. B. Caldona, A. C. C. De Leon, P. G. Thomas, D. F. Naylor, B. B. Pajarito and R. C. Advincula, Superhydrophobic Rubber-Modified Polybenzoxazine/SiO₂ Nanocomposite Coating with Anticorrosion, Anti-Ice, and Superoleophilicity Properties, *Ind. Eng. Chem. Res.*, 2017, **56**(6), 1485–1497.
- 145 X. Li, Y. Wang, R. Wang, S. Wang, D. Zang and X. Geng, A Dip-Decoating Process for Producing Transparent Bi-Superhydrophobic and Wrinkled Water Surfaces, *Adv. Mater. Interfaces*, 2018, **5**(15), 1800356.
- 146 L. F. Pereira, Jr O. Lima, É. Margalho, C. Pinheiro, I. Rocha Segundo and J. Oliveira Carneiro, Application of nano-TiO₂ and micro-ZnO on cementitious surfaces for self-cleaning façades by spray coating and dip coating: A comparative study, *J. Build. Pathol. Rehabil.*, 2025, **10**(1), 16.
- 147 L. Xu, R. G. Karunakaran, J. Guo and S. Yang, Transparent, Superhydrophobic Surfaces from One-Step Spin Coating of Hydrophobic Nanoparticles, *ACS Appl. Mater. Interfaces*, 2012, **4**(2), 1118–1125.
- 148 H. Ye, L. Zhu, W. Li, H. Liu and H. Chen, Simple spray deposition of a water-based superhydrophobic coating with high stability for flexible applications, *J. Mater. Chem. A*, 2017, **5**(20), 9882–9890.
- 149 D. Shirole, G. Volpatti, A. Guerini, D. Zampini, G. Cusatis and A. F. Rotta Loria, Effects of electrodeposition in concrete mediated by electric currents of variable polarity, *Cem. Concr. Res.*, 2023, **172**, 107254.
- 150 R. P. S. Chakradhar, G. Prasad, P. Bera and C. Anandan, Stable superhydrophobic coatings using PVDF–MWCNT nanocomposite, *Appl. Surf. Sci.*, 2014, **301**, 208–215.
- 151 S. M. R. Razavi, J. Oh, S. Sett, L. Feng, X. Yan, M. J. Hoque, *et al.*, Superhydrophobic Surfaces Made from Naturally Derived Hydrophobic Materials, *ACS Sustain. Chem. Eng.*, 2017, **5**(12), 11362–11370.
- 152 M. Shigrekar and V. Amdoskar, A review on recent progress and techniques used for fabricating superhydrophobic coatings derived from biobased materials, *RSC Adv.*, 2024, **14**(44), 32668–32699.
- 153 S. Barthwal, S. Uniyal and S. Barthwal, Nature-Inspired Superhydrophobic Coating Materials: Drawing Inspiration from Nature for Enhanced Functionality, *Micromachines*, 2024, **15**(3), 391.
- 154 J. Lyu, B. Wu, N. Wu, C. Peng, J. Yang, Y. Meng, *et al.*, Green preparation of transparent superhydrophobic coatings



- with persistent dynamic impact resistance for outdoor applications, *Chem. Eng. J.*, 2021, **404**, 126456.
- 155 L. Fan, M. Xia, J. Liu, B. Li, T. Zhu, Y. Zhao, *et al.*, Fabrication of Superhydrophobic Coatings by Using Spraying and Analysis of Their Anti-Icing Properties, *Coatings*, 2023, **13**(10), 1792.
- 156 M. M. Frota, A. L. A. Mattos, K. W. E. Miranda, H. N. Cheng, A. Biswas and M. D. S. R. Bastos, Superhydrophobic systems in food science and technology: Concepts, trends, challenges, and technological innovations, *Appl. Food Res.*, 2022, **2**(2), 100213.
- 157 Y. A. Mehanna, E. Sadler, R. L. Upton, A. G. Kempchinsky, Y. Lu and C. R. Crick, The challenges, achievements and applications of submersible superhydrophobic materials, *Chem. Soc. Rev.*, 2021, **50**(11), 6569–6612.
- 158 S. A. Farooq, A. Raina, S. Mohan, R. Arvind Singh, S. Jayalakshmi and M. Irfan Ul Haq, Nanostructured Coatings: Review on Processing Techniques, Corrosion Behaviour and Tribological Performance, *Nanomaterials*, 2022, **12**(8), 1323.
- 159 J. Hao, K. Zhang, P. Ren, J. Chen, M. Wang, Y. Zhang, *et al.*, Tuning the wettability, mechanical and tribological properties of NbN films by doping rare earth cerium, *J. Alloys Compd.*, 2020, **814**, 152339.
- 160 T. J. Young, J. Jackson, S. Roy, H. Ceylan and S. Sundararajan, Tribological behavior and wettability of spray-coated superhydrophobic coatings on aluminum, *Wear*, 2017, **376–377**, 1713–1719.
- 161 B. S. Yilbas, B. Bhushan, B. J. Abdul Aleem and Z. Gaseem, Tribology and Superhydrophobicity of Laser-Controlled-Melted Alumina Surfaces with Hard Particles, *JOM*, 2014, **66**(6), 1068–1079.
- 162 J. Guo, F. Wang, J. J. Liou and Y. Liu, Preparation and Tribological Properties of a Superhydrophobic TB6 Titanium Alloy, *Mater. Res.*, 2023, **26**, e20220446.
- 163 M. Li, Y. Li, F. Xue and X. Jing, A robust and versatile superhydrophobic coating: Wear-resistance study upon sandpaper abrasion, *Appl. Surf. Sci.*, 2019, **480**, 738–748.
- 164 Y. Song, R. Premachandran Nair, M. Zou and Y. A. Wang, Adhesion and friction properties of micro/nano-engineered superhydrophobic/hydrophobic surfaces, *Thin Solid Films*, 2010, **518**(14), 3801–3807.
- 165 L. Wang, J. Yang, Y. Zhu, Z. Li, T. Sheng, Y. M. Hu, *et al.*, A study of the mechanical and chemical durability of Ultra-Ever Dry Superhydrophobic coating on low carbon steel surface, *Colloids Surf., A*, 2016, **497**, 16–27.
- 166 C. Antonini, A. Amirfazli and M. Marengo, Drop impact and wettability: From hydrophilic to superhydrophobic surfaces, *Phys. Fluids*, 2012, **24**(10), 102104.
- 167 X. Zhao, D. S. Park, J. Choi, S. Park, S. A. Soper and M. C. Murphy, Robust, transparent, superhydrophobic coatings using novel hydrophobic/hydrophilic dual-sized silica particles, *J. Colloid Interface Sci.*, 2020, **574**, 347–354.
- 168 Y. Rahmawan, L. Xu and S. Yang, Self-assembly of nanostructures towards transparent, superhydrophobic surfaces, *J. Mater. Chem. A*, 2013, **1**(9), 2955–2969.
- 169 X. Ren, H. Zou, Q. Diao, C. Wang, Y. Wang, H. Li, *et al.*, Surface modification technologies for enhancing the tribological properties of cemented carbides: A review, *Tribol. Int.*, 2023, **180**, 108257.
- 170 V. A. Levchenko, I. A. Buyanovskii, A. N. Bol'shakov and V. N. Matveenko, Green Tribology: Orientation Properties of Diamond-Like Carbon Coatings of Friction Units in Lubricating Media, *Russ. J. Appl. Chem.*, 2019, **92**(12), 1603–1615.
- 171 H. Huang, W. Lu, Q. Yang, Y. Zhang, H. Hu, Z. Feng, *et al.*, Double-template-regulated biomimetic construction and tribological properties of superdispersed calcium borate@polydopamine/cellulose acetate-laurate nanocomposite, *Int. J. Biol. Macromol.*, 2023, **233**, 123552.
- 172 M. A. Mohammed, Structural, Optical, Electrical and Gas Sensor Properties of ZrO₂ Thin Films prepared by Sol-Gel Technique, *NeuroQuantology*, 2020, **18**(3), 22–27.
- 173 Z. Zhang, G. Ji and Z. Shi, Tribological properties of ZrO₂ nanofilms coated on stainless steel in a 5% NaCl solution, distilled water and a dry environment, *Surf. Coat. Technol.*, 2018, **350**, 128–135.
- 174 Y. Gu, K. Xia, D. Wu, J. Mou and S. Zheng, Technical Characteristics and Wear-Resistant Mechanism of Nano Coatings: A Review, *Coatings*, 2020, **10**(3), 233.
- 175 M. Fuseini, M. M. Yousry Zaghoul, D. Abakar and M. M. Yousry Zaghoul, Review of epoxy nano-filled hybrid nanocomposite coatings for tribological applications, *FlatChem*, 2025, **49**, 100768.
- 176 C. Min, Z. Sun, Q. Li, H. Yu, Z. Xu and H. Liang, Three-dimensional interconnected graphene architecture reinforced epoxy composite with superior mechanical and tribological properties, *J. Mater. Res. Technol.*, 2023, **27**, 2563–2576.
- 177 N. Zhang, C. Qu, S. Li, C. Wang, M. Xu, Z. Yang, *et al.*, Significantly enhanced tribology and thermal management by dual-network graphene/epoxy composites, *Tribol. Int.*, 2021, **164**, 107239.
- 178 W. She, J. Yang, J. Hong, D. Sun, S. Mu and C. Miao, Superhydrophobic concrete with enhanced mechanical robustness: Nanohybrid composites, strengthen mechanism and durability evaluation, *Constr. Build. Mater.*, 2020, **247**, 118563.
- 179 H. Wang, X. Qi, L. Liang, Y. Wang, J. Zhang and X. Meng, Tribological properties of graphene oxide reinforced PPTA/PTFE composites, *J. Mater. Res. Technol.*, 2023, **23**, 3505–3514.
- 180 Z. Xiong, W. Zhang, Q. Wu, G. Wang, F. Ma, X. Wang, *et al.*, Constructing a superhydrophobic coating of dual-metal (Mo, Ni) MOF on magnesium alloy surface with excellent corrosion resistance and tribological performance, *Prog. Org. Coat.*, 2025, **200**, 109010.
- 181 Z. Gemici, H. Shimomura, R. E. Cohen and M. F. Rubner, Hydrothermal Treatment of Nanoparticle Thin Films for Enhanced Mechanical Durability, *Langmuir*, 2008, **24**(5), 2168–2177.
- 182 Y. C. Jung and B. Bhushan, Mechanically Durable Carbon Nanotube–Composite Hierarchical Structures with



- Superhydrophobicity, Self-Cleaning, and Low-Drag, *ACS Nano*, 2009, 3(12), 4155–4163.
- 183 B. R. Resendiz Diaz and C. Crick, Superhydrophobic coatings with environmentally friendly materials, in *Superhydrophobic Coating - Recent Advances in Theory and Applications*, ed. Ou J., IntechOpen; 2023, <https://www.intechopen.com/chapters/1165290>.
- 184 J. Zhao, X. Gao, S. Chen, H. Lin, Z. Li and X. Lin, Hydrophobic or superhydrophobic modification of cement-based materials: A systematic review, *Composites, Part B*, 2022, 243, 110104.
- 185 G. Cappelletti, P. Fermo and M. Camiloni, Smart hybrid coatings for natural stones conservation, *Prog. Org. Coat.*, 2015, 78, 511–516.
- 186 H. Lin, Y. Wang, Y. Gan, H. Hou, J. Yin and X. Jiang, Simultaneous Formation of a Self-Wrinkled Surface and Silver Nanoparticles on a Functional Photocuring Coating, *Langmuir*, 2015, 31(43), 11800–11808.
- 187 K. Tu, X. Wang, L. Kong and H. Guan, Facile preparation of mechanically durable, self-healing and multifunctional superhydrophobic surfaces on solid wood, *Mater. Des.*, 2018, 140, 30–36.
- 188 F. Pino, P. Fermo, M. La Russa, S. Ruffolo, V. Comite, J. Baghdachi, *et al.*, Advanced mortar coatings for cultural heritage protection. Durability towards prolonged UV and outdoor exposure, *Environ. Sci. Pollut. Res.*, 2017, 24(14), 12608–12617.
- 189 S. Xu, Q. Wang, X. Zhuo and N. Wang, Green Fabrication of Superhydrophobic Zeolite Coating on Cement-Based Material Surfaces to Improve Water-Resistant and Anticorrosion Properties, *J. Mater. Civ. Eng.*, 2024, 36(5), 04024054.
- 190 J. Song, Y. Li, W. Xu, H. Liu and Y. Lu, Inexpensive and non-fluorinated superhydrophobic concrete coating for anti-icing and anti-corrosion, *J. Colloid Interface Sci.*, 2019, 541, 86–92.
- 191 D. Aslanidou, I. Karapanagiotis and C. Panayiotou, Tuning the wetting properties of siloxane-nanoparticle coatings to induce superhydrophobicity and superoleophobicity for stone protection, *Mater. Des.*, 2016, 108, 736–744.
- 192 K. Manoharan and S. Bhattacharya, Superhydrophobic surfaces review: Functional application, fabrication techniques and limitations, *J. Micromanuf.*, 2019, 2(1), 59–78.
- 193 S. Ghosh, B. Nitin, S. Remanan, Y. Bhattacharjee, A. Ghorai, T. Dey, *et al.*, A Multifunctional Smart Textile Derived from Merino Wool/Nylon Polymer Nanocomposites as Next Generation Microwave Absorber and Soft Touch Sensor, *ACS Appl. Mater. Interfaces*, 2020, 12(15), 17988–18001.
- 194 A. Hooda, M. S. Goyat, J. K. Pandey, A. Kumar and R. Gupta, A review on fundamentals, constraints and fabrication techniques of superhydrophobic coatings, *Prog. Org. Coat.*, 2020, 142, 105557.
- 195 H. Zhao, Q. Wang, R. Shang and S. Li, Development, Challenges, and Applications of Concrete Coating Technology: Exploring Paths to Enhance Durability and Standardization, *Coatings*, 2025, 15(4), 409.
- 196 Y. Lai, Y. Tang, J. Gong, D. Gong, L. Chi, C. Lin, *et al.*, Transparent superhydrophobic/superhydrophilic TiO₂-based coatings for self-cleaning and anti-fogging, *J. Mater. Chem.*, 2012, 22(15), 7420.
- 197 H. Wang, Y. Xue, J. Ding, L. Feng, X. Wang and T. Lin, Durable, Self-Healing Superhydrophobic and Superoleophobic Surfaces from Fluorinated-Decyl Polyhedral Oligomeric Silsesquioxane and Hydrolyzed Fluorinated Alkyl Silane, *Angew. Chem., Int. Ed.*, 2011, 50(48), 11433–11436.

