

Reaction Chemistry & Engineering

Linking fundamental chemistry and engineering to create scalable, efficient processes

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: I. Al Aslani, G. Lezcano, J. M. Colom, A. Alahmadi, T. Shoinkhorova, A. Dikhtiarenko, M. Cui, L. Alfilfil, S. Alsalman, I. Moralesosorio, K. A. Al-Majnouni, P. Castaño and J. Gascon, *React. Chem. Eng.*, 2026, DOI: 10.1039/D5RE00525F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Water and Methanol Cofeeding Modulate Kinetics in Crude-to-Chemicals Cracking

Isa Al Aslani^c, Juan Manuel Colom^a, Gontzal Lezcano^b, Arwa Alahmadi^a, Tuiana Shoinkhorova^a, Alla Dikhtiarenko^d, Mengmeng Cui^b, Lujain Alfilfil^c, Sultan Alsalman^c, Isidoro Morales Osorio^c, Khalid Almajnoui^c, Pedro Castaño^{b,e,*}, Jorge Gascon^{a,e,*}

^a *Advanced Catalytic Materials, KAUST Catalysis Center (KCC), King Abdullah University of Science and Technology (KAUST), Thuwal, 23955-6900, Saudi Arabia.*

^b *Multiscale Reaction Engineering, KAUST Catalysis Center (KCC), King Abdullah University of Science and Technology (KAUST), Thuwal, 23955-6900, Saudi Arabia.*

^c *Sustainable Fuels & Chemicals Group, Aramco Research Center (ARC), Thuwal, 23955-6900, Saudi Arabia.*

^d *Imaging and Characterization Department, KAUST Core Laboratories, King Abdullah University of Science and Technology (KAUST), Thuwal, 23955-6900, Saudi Arabia.*

^e *Chemical Engineering Program, Physical Science and Engineering (PSE) Division, King Abdullah University of Science and Technology (KAUST), Thuwal, 23955-6900, Saudi Arabia.*

* Corresponding authors: pedro.castano@kaust.edu.sa, jorge.gascon@kaust.edu.sa

Abstract

The co-processing of crude oil with green methanol offers a promising pathway for integrating renewable carbon into conventional refining, yet the presence of water or any hydrophilic components such as methanol, can significantly influence catalyst performance, reaction selectivity, and overall process efficiency. We discuss experimental and kinetic modeling aspects of cofeeding water and methanol during crude oil catalytic cracking over a wide range of temperatures (525 °C-650 °C) and catalyst-to-oil ratios (0-4.14) using a Microactivity testing unit (MAT). During cofeeding, yields of gas and coke, and propylene-to-ethylene ratio fluctuated at low and high catalyst-to-oil ratios, respectively. Interestingly, cofeeding water and methanol lowered coke formation, while higher selectivity to light olefins over paraffins was observed in the presence of only water. Reparameterization of the kinetic model for Arabian Light crude using water cofeeding data revealed changes in the intrinsic kinetic parameters of the cracking reactions. Specifically, the rate constant for the monomolecular cracking



pathway leading to propylene increased across the entire temperature range, while the rate constants associated with condensation reactions, responsible for generating coke precursors, were reduced.

Keywords: catalytic cracking, kinetic modeling, micro-activity testing (MAT) unit, crude oil to chemicals, cofeeding

1. Introduction

Blending crude oil with green methanol in co-processing schemes enables the introduction of renewable carbon into established refining operations. Understanding the effect of water is essential for interpreting methanol cofeeding behavior, as water, whether introduced with the methanol feed or produced during reaction, can modify catalyst performance, influence product selectivity, and affect overall process efficiency. Notably, in direct crude-to-chemicals conversion, deliberate water cofeeding has been reported to provide beneficial effects [1, 2]. The cofeeding of water has been proposed by previous studies in oil conversion processes due to several reasons: it is a cheap diluent and heat carrier [3-5], feed atomizer [6], hydrogen donor and coke gasifying agent [4, 5, 7, 8], promoter for monomolecular reactions leading to higher selectivity to light olefins [4, 5, 7-9] and sweeper for coke precursors from the catalyst surface [10, 11]. On the other hand, methanol cofeeding [12, 13] has been shown to increase the production of light olefins at low severity [8] and the production of carbon monoxide, carbon dioxide and alkylated benzenes at high severity [14-19].

Care should be taken when comparing the impact of cofeeding on model compounds with markedly different chain lengths [20-23], as such differences can lead to ambiguous or misleading interpretations. Corma et al. used in-situ infrared spectroscopy to indicate that there is no interaction of water with the acid sites at typical cracking temperatures of n-hexadecane and hence it acts similarly to nitrogen [24] whereas they concluded that water does interact with the active sites in n-heptane cracking leading to reversible deactivation [6]. Similarly, it was concluded by Corma et al. that there is no benefit in using steam when cracking hydrocarbon fractions that can be very easily evaporated [6]. In addition, Brait et al. reported that water cofeeding effect on coke deposition in n-hexane cracking is insignificant while all reaction rates were lowered due to competitive adsorption [25]. Moreover, results from reactions in steel reactors might differ from quartz as iron oxides on the surface of steel reactors can be reduced



during the reaction [26]. Cofeeding affects also catalyst stability and the type of deposited coke. Steam cofeeding produces irreversible dealumination [3] hence rare-earth metals [27], phosphorus [28] and copper [29] can be incorporated to increase the stability of the zeolite framework, but can affect the acidic and basic properties [30]. Moreover, steam cofeeding lead to more aliphatic and less aromatic coke in crude oil cracking [10] while the opposite was reported for n-hexane cracking [31].

Kang et al. [32] explored a catalytic cracking process combining naphtha and methanol, where both substances undergo simultaneous cracking. During the study, it was discovered that optimizing the introduction points of naphtha and methanol in a circulating fluidized-bed reactor significantly enhances the yield of light olefins [32]. Pan et al. [33-36], found that methanol can improve the selectivity of light olefins during heavy oil fluid catalytic cracking, demonstrating its viability as a partial feedstock for this process.

Nowadays, novel strategies have emerged to boost the yields of both liquid products and light olefins through methanol cofeeding, such as the approach proposed by Yuan et al. [37], involving continuous membrane emulsification. Moreover, Pan et al. [33] suggested that methanol should be fed before the oil at the bottom of the riser, which could be beneficial to the methanol conversion to light olefins. They concluded that feeding methanol at the bottom of riser could enhance the heavy oil conversion in comparison with the maximum gas and diesel technology of fluid catalytic cracking. Similarly, it has been reported that, ideally, methanol should be mixed with the catalyst prior to blending with the oil to shield the catalyst from coke deposition at the beginning of the reaction, most likely due to the formation of steam during the conversion of the alcohol [33].

Yan et al. [38] reported that the overall activation energy is lowered by cofeeding water and methanol in light naphtha catalytic cracking. Corma et al. [24] found that the adsorption equilibrium constant of water and nitrogen are much lower than n-hexadecane at temperatures higher than 400°C. Moreover, n-hexadecane with cofeeding has a higher kinetic rate constant due to better contact between the feed and the catalyst [24] with an intersection between the slopes of with and without steam cofeeding over temperature for n-heptane cracking [6]. Other studies have proposed kinetic models with water cofeeding, but without a comparison with the no-cofeeding case. [39, 40].



On the other hand, few studies have discussed the effect of cofeeding on the kinetic parameters. For example, Zhao et al. concluded that steam is decreasing the activation energies for all the elementary reactions in the catalytic cracking of 2-methylpentane [21]. Al-Shafei et al. found that steam cofeeding has decreased the activation energies and increased the reaction rate constants for all primary cracking reactions (except the reaction rate constant for the reaction leading to LPG) in steam catalytic cracking of n-dodecane [41].

In a previous work from this group, we reported a kinetic model based on a simple but significant reaction network for the catalytic cracking of Arabian light crude oil covering wide ranges of temperature and catalyst-to-oil ratios [42]. In this work, we examined the influence of cofeeding under comparable temperature ranges and catalyst-to-oil ratios. For the case of water cofeeding, the kinetic parameters were reparameterized accordingly. The findings of this study provide a foundation for future multiphase simulations that incorporate deactivation and dilution effects.

2. Methodology

A micro-activity testing unit is used to investigate the catalytic cracking of Arabian light crude with water and methanol cofeeding using a physically mixed formulation consisting of two parent catalysts based on Faujasite (FAU) and ZSM-5 zeolites [10]. Catalytic cracking experiments were performed with combinations of Arabian Light, water and methanol in the temperature range from 525 °C to 650 °C and catalyst-to-oil ratio range (0–4.14).

2.1 Catalyst

For the preparation of the catalysts, equal weights of two parent zeolites (P/ZSM-5 and Faujasite) (Zeolyst) were physically mixed with kaolin clay (Sigma-Aldrich), 800 nm silicon carbide (US Research Nanomaterials), and an aluminum chlorohydrate binder ($\text{Al}_2(\text{OH})_5\text{Cl}$) (Spectrum) to create the ACM-101-PM catalyst [10]. Following the slurry preparation, a laboratory-scale spray dryer was used to shape the spherical particles (comprising 38-100 μm [10]). It is worth mentioning that, P/ZSM-5 refers to phosphorus-modified ZSM-5 zeolite. Phosphorus modification improves hydrothermal stability and



reduces excessive acidity, which helps suppress undesired hydrogen transfer reactions and coke formation during cracking.

View Article Online
DOI: 10.1039/D5RE00525F

To increase the catalyst's resistance to water dealumination during testing, the drying procedure was followed by calcination at 150 °C for one hour and steam treatment at 810 °C for seven hours (90% steam). Details are shown in the table below:

Table 1. Composition of the ACM-101-PM catalyst and its two single-zeolite component systems [10].

Composition	Single-zeolite system (wt%)		ACM-101-PM After mixing (50:50 wt%)
	FAU-only	P/ZSM-5-only	
Kaolin clay	20	20	20
800-nm SiC additive	20	20	20
Faujasite zeolite (SAR = 30)	40	-	20
P/ZSM-5 (SAR = 23, P:Al = 0.4)	-	40	20
Al ₂ O ₃ binder	20	20	20

Notes: ACM: Advanced Catalytic Materials group, FAU: faujasite, SAR: silica to alumina molar ratio, PM: physically mixed, ZSM: Zeolite Socony Mobil.

2.2 Experimental program

A total of 48 catalytic cracking experiments with Arabian Light crude oil, matching the temperature range (525-650 °C) and catalyst-to-oil ratio range (0-4.14) reported in [42], were repeated under two cofeeding conditions for direct comparison with the previous dataset: (i) 20 vol% water (AL + W(0.2)) and (ii) 10 vol% water with 10 vol% methanol (AL + W(0.1) + M(0.1)). In addition, several supplementary experiments were conducted to assess the influence of varying water and methanol contents (Table 2). Deionized water and methanol (99.9%, HPLC grade) were introduced via a separate syringe pump and combined with the crude oil stream in a T-shaped mixing joint prior to entering the reactor. Cofeeding kinetic parameters were determined by reparameterizing the previously established model using the new experimental data.

In each run, 1.33 g of oil was fed into the reactor over 75 s, after which any residual oil was purged from the catalyst bed using a nitrogen stream. Product gases were analyzed by gas chromatography (Thermo Scientific Trace 1310) equipped with one FID detector for hydrocarbon measurement and one TCD detector for N₂ and H₂ measurements. Coke formation was quantified by burning the spent catalyst at 720 °C and analyzing the evolved carbon species with an infrared analyzer.



Table 2. Additional experiments to the full sets of AL+W(0.2) and AL+W(0.1)+M(0.1) varying the content of water and methanol performed at 625°C.

Experiment Code	Water (vol%)	Methanol (vol%)	Hydrocarbon feed density (g ml ⁻¹)	C/O
AL+W(0.1)	10	0	0.866	0.940
AL+W(0.3)	30	0	0.866	0.940
AL+W(0.4)	40	0	0.866	0.940
AL+W(0.5)	50	0	0.866	0.940
AL+M(0.1)	0	10	0.859	0.853
AL+M(0.2)	0	20	0.851	0.765
AL+M(0.3)	0	30	0.844	0.675
AL+M(0.4)	0	40	0.836	0.583
AL+M(0.5)	0	50	0.829	0.490
AL+W(0.25)+M(0.25)	25	25	0.841	0.644
AL+W(0.33)+M(0.17)	33	17	0.848	0.722
AL+W(0.17)+M(0.33)	17	33	0.837	0.585

Notes: C/O: catalyst-to-oil ratio, AL: Arabian light, W: water, M: methanol.

2.3 Reaction network

The reaction network for the catalytic cracking of Arabian Light crude oil was previously established using experimental data from a micro-activity testing (MAT) unit [42] (Figure 1), and it has been adopted in the present work. In the previous study [42], the cracking experiments were conducted at temperatures between 525 and 650 °C and catalyst-to-oil ratios from 0 to 4.14. Statistically significant reaction pathways were identified from the experimental results to define the reaction network. The hydrocarbon species were grouped into eight lumps based on chemical characteristics and boiling ranges: gas lumps (ethylene; propylene; butenes with pentenes; HC-lump comprising dry gases and other paraffins), liquid lumps (bottoms; diesel; gasoline), and coke. Interconversion between these lumps was represented by forward first-order reactions, with backward reactions allowed among the liquid lumps. The optimal kinetic model, comprising nine reactions, was selected by minimizing both the number of significant kinetic parameters and the sum of squared errors between observed and predicted yields. Model robustness and applicability to other crude oil types were confirmed by validating the kinetic parameters against Arabian Extra Light crude oil. Although additional pathways could be included (e.g., explicit methane or ethane formation), the present model focuses on dominant



lump interconversions to avoid overparametrization. Minor gas products are included within the HC-lump, consistent with previous lumped FCC kinetic models. The final reaction network was selected by eliminating statistically insignificant reaction pathways while maintaining predictive accuracy. This reduced network minimized parameter uncertainty while preserving the dominant reaction pathways governing crude oil cracking.

The complete set of rate equations and parameter estimation procedure are given in our previous work [42] as well as in the supplementary material of this study.

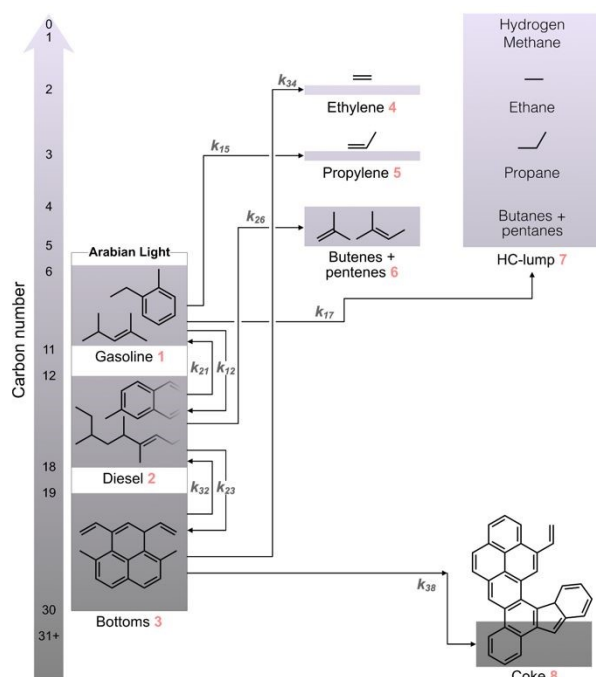


Figure 1. Reaction network for the kinetic model [42].



3. Results and discussion

View Article Online
DOI: 10.1039/D5RE00525F

3.1 Experimental data

Figure 2 shows that water addition increases the propylene-to-ethylene ratio at 525 °C under both thermal and high catalyst-to-oil ratio conditions, as evidenced by the comparison between Figure 2b (water cofeeding) and Figure 2a (no cofeeding). Similarly, Figure 2e demonstrates that water significantly reduces coke formation at high catalyst-to-oil ratios relative to Figure 2d, while the combined cofeeding of methanol and water further suppresses coke yields (Figure 2f). These observations are consistent with the catalyst surface cleaning effect previously proposed by Yan and Van Mao [12].

Cofeeding water (Figure 2h) or a water-methanol mixture (Figure 2i) enhanced conversion, reflected in higher gas and coke yields, at low catalyst-to-oil ratios compared with the baseline case (Figure 2g), primarily due to the promotion of monomolecular cracking reactions. At higher severities, however, the effect becomes negligible in some instances, consistent with the threshold proposed by Corma et al., whereby the decline in conversion is offset once the catalyst-to-oil ratio reaches four, as sufficient active sites are available [43].



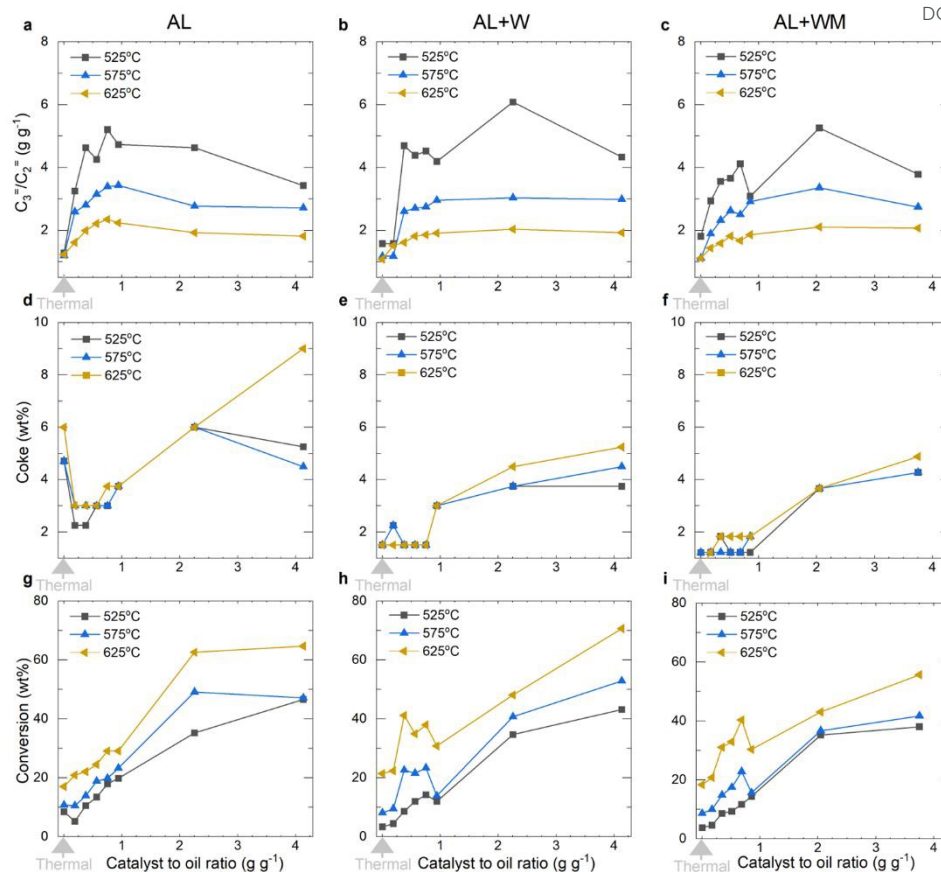


Figure 2. Propylene to ethylene ratio, coke yield and conversion for AL, AL+W(0.2) and AL+W(0.1)+M(0.1) at different temperatures and catalyst-to-oil ratios.

Figure 3 shows carbon monoxide, carbon dioxide, and hydrogen yields after cofeeding water and methanol. Methanol cofeeding produces higher amounts of carbon dioxide and hydrogen at lower temperatures while produces more carbon monoxide at higher temperatures, which agrees with the available data in the literature [44]. The second axis in Figures 3(g-i) illustrates that the increase in hydrogen yield is linked with the selectivity of paraffins over olefins. Therefore, it can be concluded that, within the high-temperature range examined in this study, methanol cofeeding does not improve olefin selectivity relative to paraffins.



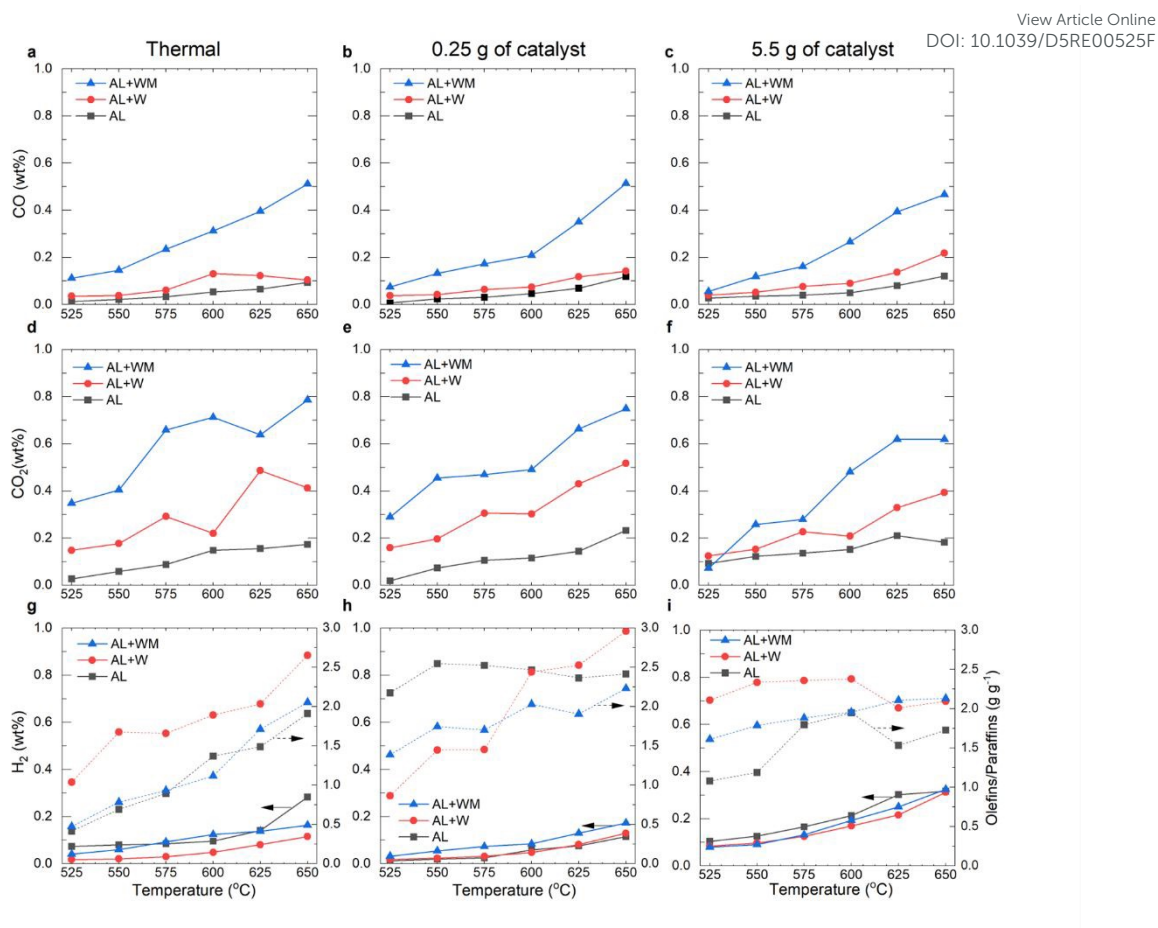


Figure 3. Carbon monoxide, carbon dioxide and hydrogen for AL, AL+W(0.2) and AL+W(0.1)+M(0.1) at different temperatures and amount of catalyst loadings.

Methanol cofeeding enhances isomerization reactions in both the gasoline fraction (Figures 4a,e) and the gas phase (Figures 4b,f) to a greater extent than water cofeeding alone under thermal cracking and in most catalytic cracking conditions. At high temperature, methanol's contribution to increased isoparaffin formation becomes more pronounced at higher temperatures. This observed enhancement in isomerization products aligns with the findings of [21], where water was shown to promote isomerization in 2-methylpentane cracking over ultra-stable Y zeolite at elevated temperatures with heavy feeds.

In Figures 4c,g, combined water and methanol cofeeding increases the olefin-to-aromatic ratio under thermal conditions and at low catalyst-to-oil ratios. However, this effect diminishes in the remaining cases, likely due to the enhancement of aromatic production via hydrogen transfer reactions [10]. Furthermore, as illustrated in Figures 4d,h, the introduction of water and methanol promotes the



alkylation of benzene to toluene and xylenes at low temperatures and catalyst-to-oil ratios, an effect attributed to methyl radicals generated from methanol [14-17, 19].

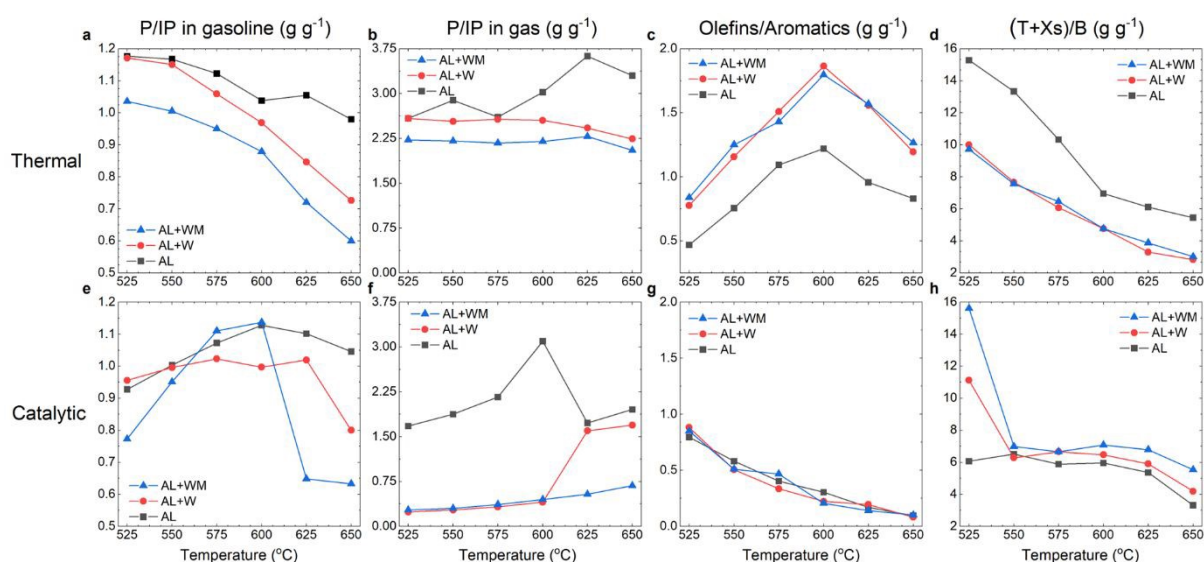


Figure 4. Paraffins to Isoparaffins ratio in gasoline (a,e) and gas (n-butane + n-pentane to i-butane + i-pentane) (b,f), olefins to aromatics in gasoline (c,g) and toluene + xylenes to benzene ratio for AL, AL+W(0.2) and AL+W(0.1)+M(0.1) at different temperatures under thermal and catalytic conditions (e,f and g)=5.5g while h=3g.

Figures 5a-d present additional experiments, which were conducted to evaluate the influence of varying water and methanol fractions on product distribution under fixed catalytic conditions (625 °C and 1.25g catalyst). The objective was to identify trends in light olefin formation, coke production, and selectivity ratios as a function of cofeed composition. The highest light olefins yield, 30 wt%, was obtained at a composition of $W = 0.4$ and $M = 0$ (volume fractions), while the maximum propylene-to-ethylene ratio of 2.3 occurred at $W = 0.33$ and $M = 0.17$. Light olefins yield peaked at 30 vol% methanol, in agreement with the findings of Yan et al. [12].

However, increasing methanol content also led to a pronounced rise in coke formation (Figure 5c) and HC-lump production (Figure 5d), accompanied by a relatively smaller increase in light olefins yield (Figure 5a), largely due to elevated methane production. These results reinforce the conclusion from the previous experiments that methanol cofeeding does not improve selectivity toward light olefins. Indeed,



previous studies have reported that methanol cofeeding tends to favor methane formation over light olefins, particularly when catalyst activity is reduced by coke deposition [33].

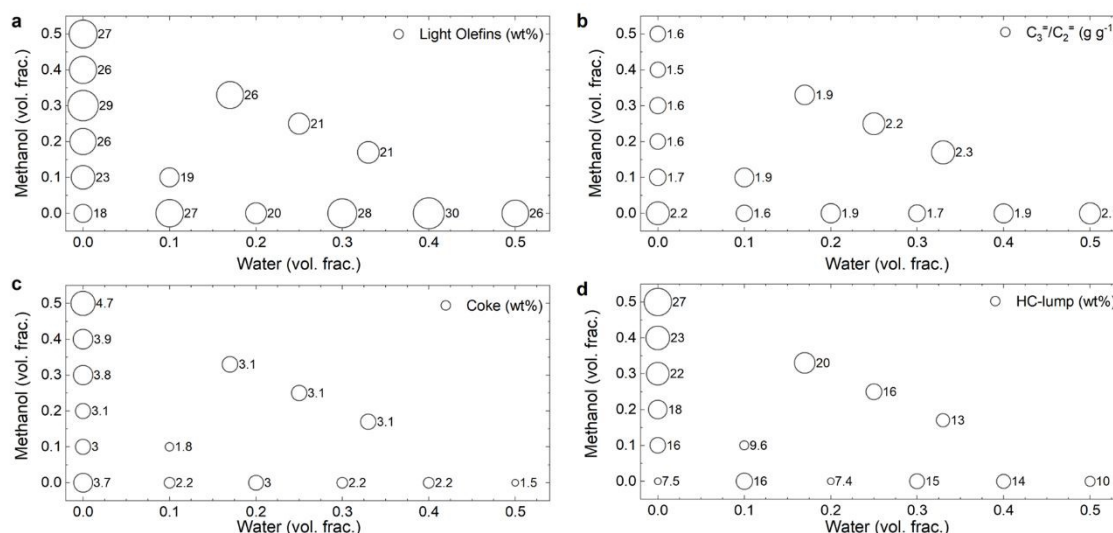


Figure 5. Light olefins (a), yields and propylene to ethylene ratio (b), coke (c) and HC-lump (d) for several content values of methanol and water at catalyst loading of 1.25g and 625°C.

The effects of water and methanol cofeeding on thermal, monomolecular, and bimolecular reactions can be summarized as follows. In thermal reactions, water and methanol increase the propylene-to-ethylene ratio at 525 °C and markedly suppress coke formation. At 625 °C, they enhance conversion, raising CO, CO₂, and olefins-to-paraffins ratios, though the latter decreases when methanol is cofed with water. Both additives also promote isomerization in gas and liquid phases and increase the olefin-to-aromatic ratio in liquids under thermal conditions.

For monomolecular reactions, cofeeding particularly boosts conversion and propylene-to-ethylene ratios at low catalyst-to-oil ratios and higher temperatures. In bimolecular reactions, water and methanol significantly suppress coke formation at high catalyst loadings, thereby improving catalyst activity. Ethylene and propylene formation via oligomerization–cracking of butenes and pentenes is also observed (see supplementary figures). Overall, high-temperature thermal cracking remains critical due to its link with paraffin and syngas production, reflecting the complex interplay of reaction pathways reported in prior studies.

3.2 Kinetic model



Table 3 presents the fitted kinetic parameters obtained from the water cofeeding experiments, alongside the corresponding parameters from the no-cofeeding dataset for comparison [42]. Where $E_{a,ij}$ is the apparent activation energy and $k_{0,ij}$ is the rate constant at the reference temperature (600 °C), which was chosen as the midpoint of the temperature range studied and facilitates the solving process [42].

The correlated variations in the kinetic parameters for all reactions, except diesel to bottoms, bottoms to coke, and bottoms to ethylene, can be attributed to changes in surface coverage induced by steam cofeeding [6]. The difference between forward and backward activation energies increased for the bottoms–diesel conversion (from -38 to -75 kJ mol⁻¹) and decreased for the diesel-gasoline conversion (from -15 to -2.7 kJ mol⁻¹). This suggests that water cofeeding promotes hydrogen transfer reactions in long-chain molecules (-85.5 kJ mol⁻¹) and isomerization reactions in short-chain molecules (-1.9 kJ mol⁻¹) over condensation pathways leading to coke precursors (-28.7 kJ mol⁻¹), as supported by density functional theory calculations [45].

Table 3. Kinetic parameters obtained with water cofeeding data compared with the no-cofeeding case, $R^2=0.92$.

Reaction	$k_{0,ij}$ (s ⁻¹)		$E_{a,ij}$ (kJ mol ⁻¹)	
	AL	AL+W	AL	AL+W
Bottoms to diesel (k_{32})	23.2 (± 3.1)	12.3 (± 3.30)	111.2 (± 18.0)	97.5 (± 25.9)
Diesel to bottoms (k_{23})	7.75 (± 1.90)	3.06 (± 2.39)	149.5 (± 35.7)	172.3 (± 81.2)
Bottoms to coke (k_{38})	2.29 (± 0.35)	1.34 (± 0.38)	72.8 (± 20.5)	86.1 (± 41.5)
Bottoms to ethylene (k_{34})	1.85 (± 0.35)	1.59 (± 0.47)	126.3 (± 30.6)	151.1 (± 47.4)
Diesel to gasoline (k_{21})	85.9 (± 10.8)	64.7 (± 13.9)	177.4 (± 20.0)	146.9 (± 28.9)
Gasoline to diesel (k_{12})	69.6 (± 10.1)	60.3 (± 13.3)	191.9 (± 23.9)	149.6 (± 30.0)
Diesel to butenes + pentenes (k_{26})	1.77 (± 0.22)	1.89 (± 0.32)	46.2 (± 17.1)	58.7 (± 23.8)
Gasoline to propylene (k_{15})	2.56 (± 0.25)	3.10 (± 0.41)	71.1 (± 14.1)	73.2 (± 19.6)
Gasoline to HC-lump (k_{17})	2.52 (± 0.24)	2.67 (± 0.38)	61.9 (± 13.9)	79.1 (± 21.5)

Note: Values are given at a 95% confidence interval.

Figure 6 shows the evaluated rate constants over the whole temperature range. Figure 6h shows that cofeeding water increased the rate constant for the reaction to propylene at the whole temperature range, which supports the fact that water enhances monomolecular cracking reactions [46]. In addition, the increasing effect of the other reactions occurs at certain temperature levels (similar intersections in the trends were reported by [6]) for the forward (Figure 6e) and backward (Figure 6f) gasoline to diesel, diesel to butenes with pentenes (Figure 6g), and gasoline to HC-lump (Figure 6i).

Because coke accumulates during MAT experiments, catalyst activity changes during the test. Therefore, the fitted kinetic constants should be interpreted as effective parameters obtained from time-



averaged product yields over the injection period, rather than intrinsic constants at a fixed catalyst state [42].

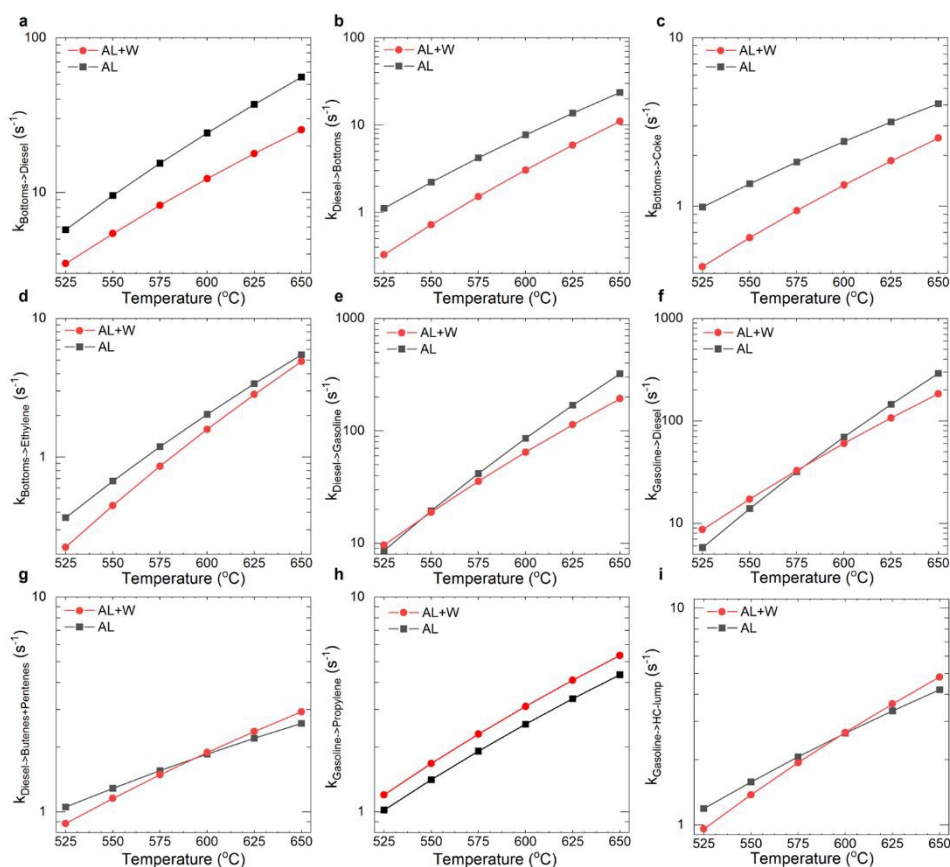


Figure 6. AL+W(0.2) and AL rate constants at the whole temperature range.

Figure 7 compares the experimental data for water cofeeding with the model predictions. Most deviations arise from the dominance of monomolecular cracking at low catalyst-to-oil ratios. While this low-ratio region is less relevant for practical fluid catalytic cracking (FCC) operation, where conversions are typically high, it remains important for developing a robust kinetic model with statistically significant parameters. The resulting model is suitable for integration into multiphase simulations, particularly once the limitations of using a micro-activity testing unit are mitigated, as discussed in [42], with water content incorporated alongside temperature and catalyst-to-oil ratio in the proposed conversion–activity correlation.



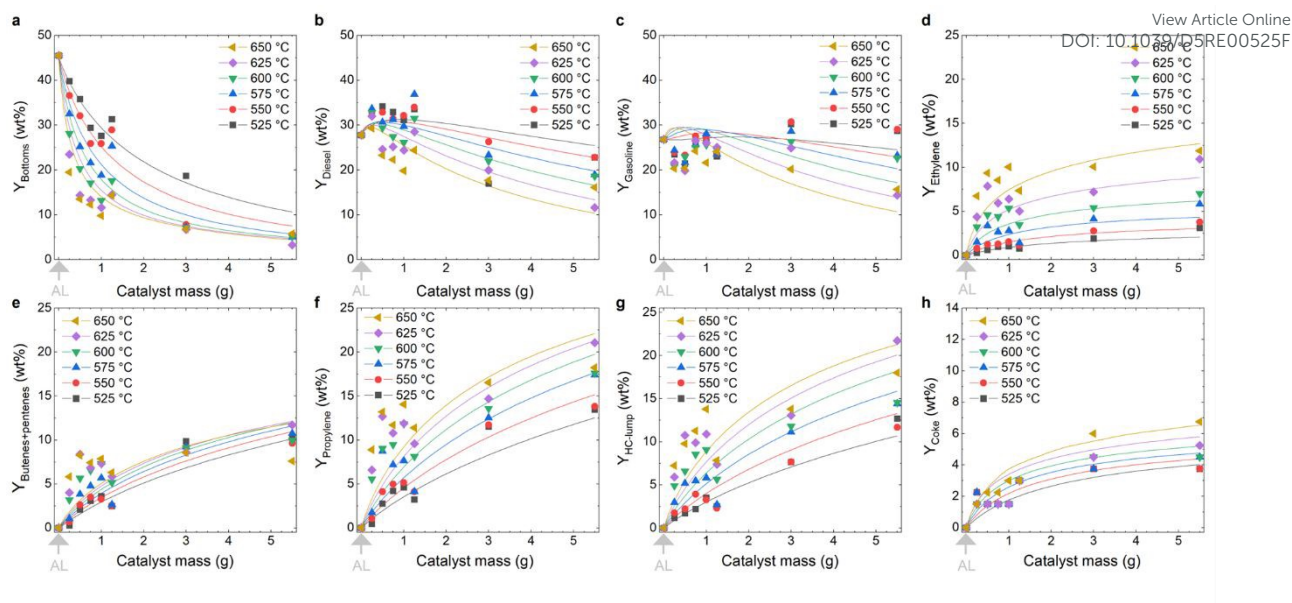


Figure 7. AL+W(0.2) data points (scattered) and the predicted yield (solid curves).

4. Conclusions

This study systematically examined the effects of cofeeding water and methanol on the catalytic cracking of Arabian Light crude oil over a broad range of operating conditions using a micro-activity testing (MAT) unit, supported by kinetic modeling. The work provides detailed insights into how these cofeeds alter reaction selectivity, coke formation, and intrinsic kinetic parameters, with implications for industrial cracking optimization. The main conclusions are:

- **Thermal reaction effects**
 - Water and methanol cofeeding at 525 °C increased the propylene-to-ethylene ratio and strongly suppressed coke formation.
 - At 625 °C, both additives enhanced conversion, increased CO and CO₂ yields, and elevated the olefin-to-paraffin ratio, although the latter decreased when methanol was cofed with water.
 - Water and methanol promoted isomerization reactions in both gas and liquid phases, and increased the olefin-to-aromatic ratio in liquids under thermal conditions.
- **Monomolecular cracking**



- Cofeeding water or water–methanol mixtures enhanced conversion and propylene-to-ethylene ratios at low catalyst-to-oil ratios, particularly at higher temperatures.

View Article Online
DOI: 10.1039/D3RE00525F

- Kinetic modeling confirmed that water cofeeding increased the rate constant for the monomolecular cracking pathway to propylene across the entire temperature range.

- **Bimolecular reactions and coke suppression**

- Water and methanol cofeeding significantly reduced coke formation at high catalyst-to-oil ratios, improving catalyst activity.
- Water addition suppressed condensation reactions responsible for coke precursor formation while promoting hydrogen transfer in heavy fractions and isomerization in light fractions.

- **Methanol-specific effects**

- Methanol cofeeding enhanced isomerization more than water alone under both thermal and most catalytic cracking conditions, with a stronger effect at high severity and temperature.
- Methanol favored alkylation of benzene to toluene and xylenes at low temperatures and catalyst-to-oil ratios, attributed to methyl radical formation.
- Increasing methanol content beyond ~30 vol% led to higher coke and HC-lump yields with relatively small gains in light olefins, due to increased methane production.
- Within the studied high-temperature range, methanol cofeeding did not improve olefin selectivity relative to paraffins and, in some cases, shifted selectivity toward paraffins.

- **Kinetic model implications**

- Reparameterization with water cofeeding data showed correlated changes in kinetic parameters for most reactions, except diesel → bottoms, bottoms → coke, and bottoms → ethylene.



- The model achieved good agreement with experimental data ($R^2 = 0.92$) and is suitable for integration into multiphase simulations when including a water-content term in the conversion–activity correlation.

Article Online
DOI: 10.1039/D5RE00525F

Overall, the combined experimental-modeling approach confirms that water cofeeding can beneficially influence FCC operation by enhancing monomolecular cracking, mitigating coke formation, and shifting selectivity, while methanol cofeeding offers selective benefits in isomerization and aromatic alkylation but does not improve light olefin selectivity at high temperatures.

Acknowledgments

This work was conducted with the financial support of Aramco and the resources and facilities provided by the King Abdullah University of Science and Technology (KAUST, BAS/1/1397-01-01).

References

- [1] M. A. Alabdullah, A. R. Gomez, J. Vittenet, A. Bendjeriou-Sedjerari, W. Xu, I. A. Abba, J. Gascon, A Viewpoint on the Refinery of the Future: Catalyst and Process Challenges, *ACS Catal.* 10 (15) (2020) 8131–8140. doi:10.1021/acscatal.0c02209.
- [2] K. Couch, G. Funk, World scale crude to olefins (2022). URL www.digitalrefining.com/article/1002842/world-scale-crude-to-olefins
- [3] A. Yamaguchi, D. Jin, T. Ikeda, K. Sato, N. Hiyoshi, T. Hanaoka, F. Mizukami, M. Shirai, Effect of steam during catalytic cracking of n-hexane using P-ZSM-5 catalyst, *Catal. Commun.* 69 (2015) 20–24. doi:10.1016/j.catcom.2015.05.015.
- [4] X. Meng, C. Xu, J. Gao, Effect of steam on heavy oil catalytic pyrolysis, *Petrol. Chem.* 47 (2) (2007) 83–86. doi:10.1134/s096554410702003X.
- [5] X. Meng, C. Xu, J. Gao, Z. Liu, Influence of feed properties and reaction conditions on catalytic pyrolysis of gas oils and heavy oils, *Fuel* 87 (12) (2008) 2463–2468. doi:10.1016/j.fuel.2008.02.003.
- [6] A. Corma, J. Mengual, P. J. Miguel, Steam catalytic cracking of naphtha over ZSM-5 zeolite for production of propene and ethene: Micro and macroscopic implications of the presence of steam, *Appl. Catal. A-Gen.* 417–418 (2012) 220–235. doi:10.1016/j.apcata.2011.12.044.
- [7] S. Shirvani, M. Ghashghaee, Combined effect of nanoporous diluent and steam on catalytic upgrading of fuel oil to olefins and fuels over USY catalyst, *Petrol. Sci. Technol.* 36 (11) (2018) 750–755. doi:10.1080/10916466.2018.1445104.
- [8] M. Ghashghaee, S. Shirvani, M. Ghambarian, S. Kegnaes, Synergistic coconversion of refinery fuel oil and methanol over H-ZSM-5 catalyst for enhanced production of light olefins, *Energy Fuel.* 33 (2019) 5761–5765. doi:10.1021/acs.energyfuels.9b00347.
- [9] E. N. Al-Shafei, Z. Qureshi, M. Z. Albahar, A. Alasseel, S. Asaoka, A. Aitani, Hierarchical ZSM-5@SiO₂ Catalysts: A Novel Approach to Optimizing Olefin Yield from Heavy Atmospheric Gas Oil, *J Phys. Chem. C* 128 (25) (2024) 10440–10449. doi:10.1021/acs.jpcc.4c03467.



[10] M. Alabdullah, A. Rodriguez-Gomez, T. Shoinkhorova, A. Dikhtiarenko, A. D. Chowdhury, I. Hita, S. R. Kulkarni, J. Vittenet, S. M. Sarathy, P. Castaño, A. Bendjeriou-Sedjerari, E. Abou-Hamad, W. Zhang, O. S. Ali, I. Morales-Osorio, W. Xu, J. Gascon, One-step conversion of crude oil to light olefins using a multi-zone reactor, *Nature Catal.* 4 (3) (2021) 233–241. doi:10.1038/s41929-021-00580-7.

[11] B. W. Wojciechowski, The reaction mechanism of catalytic cracking: Quantifying activity, selectivity, and catalyst decay, *Cataly. Rev.* 40 (1998) 209–328. doi:10.1080/01614949808007110.

[12] H. Yan, R. Le Van Mao, Mixed naphtha/methanol feed used in the thermal catalytic/steam cracking (tcsc) process for the production of propylene and ethylene, *Catal. Lett.* 141 (2011) 691–698. doi:10.1007/s10562-010-0528-4.

[13] G. A. Olah, Beyond Oil and Gas: The Methanol Economy, *Angew. Chem.* 44 (2005) 2636–2639. doi:10.1002/anie.200462121.

[14] J. Qian, G. Xiong, J. Liu, C. Liu, H. Guo, A Preliminary Study on the Role of the Internal and External Surfaces of Nano-ZSM-5 Zeolite in the Alkylation of Benzene with Methanol, *Ind. Eng. Chem. Res.* 58 (21) (2019) 9006–9016. doi:10.1021/acs.iecr.9b00291.

[15] T. Yashima, H. Ahmad, K. Yamazaki, M. Katsuta, N. Hara, Alkylation on synthetic zeolites: I. alkylation of toluene with methanol, *J Catal.* 16 (3) (1970) 273–280. doi:10.1016/0021-9517(70)90223-X.

[16] T. Yashima, K. Yamazaki, H. Ahmad, M. Katsuta, N. Hara, Alkylation on synthetic zeolites: II. selectivity of p-xylene formation, *J Catal.* 17 (2) (1970) 151–156. doi:10.1016/0021-9517(70)90088-6.

[17] T. Yashima, K. Sato, T. Hayasaka, N. Hara, Alkylation on synthetic zeolites: III. alkylation of toluene with methanol and formaldehyde on alkali cation exchanged zeolites, *J Catal.* 26 (3) (1972) 303–312. doi:10.1016/0021-9517(72)90088-7.

[18] S. Wang, Q. Cai, Z. Guo, Y. Wang, X. Wang, Renewable gasoline produced by co-cracking of methanol and ketones in bio-oil, *BioResources* 7 (4) (2012). doi:10.15376/biores.7.4.5019-5031.

[19] M. Cher, The reaction of methyl radicals with toluene, *J. Phys. Chem-US* 68 (6) (1964) 1316–1321. doi:10.1021/j100788a009.

[20] Y. Zhao, B. Wojciechowski, The consequences of steam dilution in catalytic cracking: I. effect of steam dilution on reaction rates and activation energy in 2-methylpentane cracking over ushy, *J Catal.* 163 (2) (1996) 365–373. doi:10.1006/jcat.1996.0338.

[21] Y. Zhao, B. Wojciechowski, The consequences of steam dilution in catalytic cracking: II. effect of steam dilution on the selectivity and mechanism in 2-methylpentane cracking over ushy, *J Catal.* 163 (2) (1996) 374–391. doi:10.1006/jcat.1996.0339.

[22] F. Li, X. He, C. A. Shoemaker, C. H. Wang, Experimental and numerical study of biomass catalytic pyrolysis using Ni2P-loaded zeolite: Product distribution, characterization and overall benefit, *Energ. Convers. Manage.* 208 (2020) 112581. doi:10.1016/j.enconman.2020.112581.

[23] J. Zou, L. Zhao, Q. Hu, D. Yao, H. Yang, Pyrolysis and catalytic reforming of disposable plastic waste for syngas production with adjustable H₂/CO ratio, *Appl. Energ.* 362 (2024) 122844. doi:10.1016/j.apenergy.2024.122844.

[24] A. Corma, O. Marie, F. Ortega, Interaction of water with the surface of a zeolite catalyst during catalytic cracking: a spectroscopy and kinetic study, *J Catal.* 222 (2) (2004) 338–347. doi:10.1016/j.jcat.2003.11.006.

[25] A. Brait, K. Seshan, H. Weinstabl, A. Ecker, J. A. Lercher, Evaluation of commercial FCC catalysts for hydrocarbon conversion: II. Time-on-stream behavior of n-hexane conversion and comparison of n-hexane conversion to MAT, *Appl. Catal. A-Gen.* 169 (2) (1998) 315–329. doi:10.1016/s0926-860x(98)00024-6.



- [26] J. Lachén, J. Herguido, J. A. Peña, Production and purification of hydrogen by biogas combined reforming and steam-iron process, *Int. J. Hydrogen Energ.* 44 (35) (2019) 19244–19254. doi:10.1016/j.ijhydene.2018.04.151. Article Online
DOI: 10.1039/D5RE00525F
- [27] A. Akah, J. Williams, M. Ghrami, An Overview of Light Olefins Production via Steam Enhanced Catalytic Cracking, *Catal. Surv. Asia* 23 (4) (2019) 265–276. doi:10.1007/s10563-019-09280-6.
- [28] M. Alabdullah, T. Shoinkhorova, A. Rodriguez-Gomez, A. Dikhtiarenko, J. Vittenet, O. S. Ali, I. Morales-Osorio, W. Xu, J. Gascon, Composition-performance Relationships in Catalysts Formulation for the Direct Conversion of Crude Oil to Chemicals, *ChemCatChem* 13 (7) (2021) 1806–1813. doi:10.1002/cctc.202001738.
- [29] K. Kubo, H. Iida, S. Namba, A. Igarashi, Ultra-high steaming stability of Cu-ZSM-5 zeolite as naphtha cracking catalyst to produce light olefin, *Catal. Commun.* 29 (2012) 162–165. doi:10.1016/j.catcom.2012.10.004.
- [30] W. Xiaoning, Z. Zhen, X. Chunming, D. Aijun, Z. Li, J. Guiyuan, Effects of Light Rare Earth on Acidity and Catalytic Performance of HZSM-5 Zeolite for Catalytic Cracking of Butane to Light Olefins, *J. Rare Earths* 25 (3) (2007) 321–328. doi:10.1016/s1002-0721(07)60430-x.
- [31] A. Yamaguchi, D. Jin, T. Ikeda, K. Sato, N. Hiyoshi, T. Hanaoka, F. Mizukami, M. Shirai, Deactivation of ZSM-5 zeolite during catalytic steam cracking of n-hexane, *Fuel Process. Technol.* 126 (2014) 343–349. doi:10.1016/j.fuproc.2014.05.013.
- [32] N. Y. Kang, Y. K. Park, W. C. Choi, D. J. Kim, H. M. Seo, S. S. Park, S. C. Kang, Naphtha and methanol mixed catalytic cracking reaction process, U.S. Patent No 10,131,850, 20 November 2018 (20 November 2018).
- [33] S. Y. Pan, H. Jiang, H. Weng, Feeding methanol in an FCC unit, *Petrol. Sci. Technol.* 26 (2008) 170–180. doi:10.1080/10916460600805152.
- [34] S. Y. Pan, H. Jiang, H. Weng, Feasibility analysis of methanol as a part of fluidized catalytic cracking feedstock, *Petro. Technol. (china)* 34 (12) (2005) 1153–1158.
- [35] S. Y. Pan, H. Jiang, H. Weng, Study on the reaction of methanol conversion in FCC condition, *Chem. Eng. Oil Gas (china)* 34 (5) (2005) 1153–1158.
- [36] S. Y. Pan, H. Jiang, H. Weng, Reaction of methanol as part of FCC feedstock, *J. Chem. Ind. Eng. (China)* 57 (4) (2006) 785.
- [37] C. Yuan, K. Zhou, Y. Liu, W. Jiang, W. Jing, X. Ding, T. Yu, Z. Zhong, Y. Fan, W. Jin, W. Xing, Coupling of the methanol-to-olefin (MTO) process in an FCC unit to improve the yield of light olefins via continuous membrane emulsification, *Chem. Eng. Sci.* 296 (2024) 120285. doi:10.1016/j.ces.2024.120285.
- [38] R. Yan, H. T. Le Van Mao, Catalytic Compatibility of Methanol with Petroleum Naphtha in Mixed Feeds Used in the Thermal-Catalytic/Steam-Cracking (TCSC) Process for the Production of Propylene and Ethylene, *Catal. Lett.* 142 (2012) 60–70. doi:10.1007/s10562-011-0734-8.
- [39] M. Sedighi, K. Keyvanloo, J. Towfighi, Kinetic study of steam catalytic cracking of naphtha on a Fe/ZSM-5 catalyst, *Fuel* 109 (2013) 432–438. doi:10.1016/j.fuel.2013.02.020.
- [40] Q. Xu, A. C. Akah, M. AlHerz, A. Aitani, Z. S. Qureshi, M. A. B. Siddiqui, N. Abo-Ghander, Kinetic study of crude oil-to-chemicals via steam-enhanced catalytic cracking in a fixed-bed reactor, *Can. J. Chem. Eng.* 101 (7) (2022) 4042–4053. doi:10.1002/cjce.24761.
- [41] E. N. Al-Shafei, A. N. Aljishi, Z. M. Shakoob, M. Z. Albahar, M. F. Aljishi, A. Alasseel, Steam catalytic cracking and lump kinetics of naphtha to light olefins over nanocrystalline ZSM-5 zeolite, *RSC Adv.* 13 (37) (2023) 25804–25816. doi:10.1039/d3ra03157h.
- [42] I. Al Aslani, G. Lezcano, J. M. Colom, A. Alahmadi, T. Shoinkhorova, A. Dikhtiarenko, M. Cui, L. Alfifil, I. Morales Osorio, K. Almajnoui, P. Castaño, J. Gascon, Reaction network and kinetic modeling for the direct



catalytic cracking of Arabian light crude oil to chemicals, *Chem. Eng. J.* 498 (2024) 154981. doi:10.1016/j.cej.2024.154981.

View Article Online
DOI: 10.1039/D5RE00525F

[43] A. Corma, O. Bermúdez, C. Martínez, F. Ortega, Dilution effect of the feed on yield of olefins during catalytic cracking of vacuum gas oil, *Appl. Catal. A-Gen.* 230 (1-2) (2002) 111–125. doi:10.1016/s0926-860x(01)01000-6.

[44] Y. Qi, Y.-A. Zhu, D. Chen, Mechanism investigation and catalyst screening of high-temperature reverse water gas shift reaction, *Green Chem. Eng.* 1 (2) (2020) 131–139. doi:10.1016/j.gce.2020.10.001.

[45] E. Ivanchina, E. Ivashkina, G. Nazarova, Mathematical modelling of catalytic cracking riser reactor, *Chem. Eng. J.* 329 (2017) 262–274. doi:https://doi.org/10.1016/j.cej.2017.04.098.

[46] E. N. Al-Shafei, M. Z. Albahar, M. F. Aljishi, A. N. Aljishi, G. A. Nasser, M. A. Sanhoob, A. S. Alnasir, A. AlAsseel, Effect of zeolite structure and addition of steam on naphtha catalytic cracking to improve olefin production, *Fuel* 321 (2022) 124089. doi:10.1016/j.fuel.2022.124089.



The datasets generated and analyzed during this study—including raw MAT reactor outputs, gas chromatography data, coke quantification measurements, and kinetic model input–output files—are available from the corresponding authors upon reasonable request. Due to institutional data management policies and ongoing related research activities, the full experimental dataset cannot be made publicly available at this time. All data necessary to reproduce the figures, kinetic parameter fitting, and conclusions of this work are provided within the article and its Supplementary Information.

