

Showcasing research from Professor Laleh Tahsini's laboratory, Oklahoma State University, Oklahoma, USA.

Metal ligand cooperativity in the direct carboxylation and esterification of terminal alkynes by Cu-CNC complexes bearing 2,6-lutidine linkers

This work highlights the first structurally characterized dearomatized Cu-CNC complexes and their application as catalysts for the direct carboxylation of terminal alkynes through the MLC. CO₂ utilization in direct organic synthesis is a significant and emerging field in catalysis. In this work, we report novel molecular Cu-CNC complexes that react with CO₂ and terminal alkynes under atmospheric and sub-atmospheric pressures. While copper-catalyzed carboxylation is not unprecedented, this work presents the first example of metal-ligand-cooperativity (MLC) *via* a dearomatization-aromatization mechanism in the direct carboxylation of terminal alkynes. It also presents the first dearomatized Cu-CNC complexes that have been crystallographically and spectroscopically characterized, and their enthalpy and entropy of formation, as well as the activation parameters, have been determined.

Image reproduced by permission of Laleh Tahsini from *Chem. Sci.*, 2026, **17**, 2087.

As featured in:



See Laleh Tahsini *et al.*,
Chem. Sci., 2026, **17**, 2087.

Cite this: *Chem. Sci.*, 2026, 17, 2087

All publication charges for this article have been paid for by the Royal Society of Chemistry

Metal ligand cooperativity in the direct carboxylation and esterification of terminal alkynes by Cu-CNC complexes bearing 2,6-lutidine linkers

Nick Back,^a Emylie Guthrie,^a Chengxu Zhu,^{bc} Sam P. de Visser^{bc} and Laleh Tahsini^{id}*^a

CO₂ utilization is a significant and emerging field in catalysis, playing a crucial role in reducing atmospheric CO₂ and mitigating climate change. In this work, we report on Cu(I) complexes that utilize atmospheric CO₂ for the direct carboxylation and esterification of terminal alkynes. The Cu(I) complexes bear ligands of the type 2,6-bis(3-alkyl/arylimidazol-2-ylidene) methylpyridine I(R)^{C^NA^C}, where R = ⁱPr, Me, 2,6-ⁱPr₂Ph (Dipp), 2,4,6-Me₃Ph (Mes), and 4-CF₃Ph. While copper-catalyzed carboxylation reactions are not unprecedented, this work presents the first example of metal ligand cooperativity (MLC) through a dearomatization-aromatization process used in the direct carboxylation of terminal alkynes. It also presents the first dearomatized Cu-CNC complexes that have been crystallographically and spectroscopically characterized. Further investigation using UV-vis spectroscopy revealed the enthalpy and entropy of formation, as well as the activation parameters for the dearomatized [Cu^I(I(ⁱPr)^{C^NA^C})*] complex. This marks the first time such data have been reported for dearomatized-metal-CNC systems. To establish mechanistic details of the reaction, we performed stoichiometric reactions and characterized products with a variety of NMR methods. Combined with supporting computational studies, the work yields several new CNC-supported copper intermediates, including copper-styrenyl, copper-acetylide, and copper-propiolate. While the reactive and labile nature of some of these intermediates precludes their solid-state characterization, DFT-computed structures are consistent with spectroscopic characterization.

Received 29th October 2025
Accepted 8th January 2026


DOI: 10.1039/d5sc08379f

rsc.li/chemical-science

Introduction

Catalytic carbon dioxide activation and functionalization has emerged as a critical research area. It provides a pathway for carbon recycling and contributes to the synthesis of valuable chemicals and fuels, thereby addressing the dual challenges of energy sustainability and reducing greenhouse gas emissions. The activation of CO₂ is a critical step in the conversion process due to its thermodynamic stability and kinetic inertness, requiring significant energy input. Over the last two decades, various catalysts, including transition metals,¹⁻⁴ metal-organic frameworks (MOFs),^{5,6} covalent organic frameworks (COFs),⁷ and hybrid systems combining plasma and catalysts,⁸ have been reported for CO₂ reduction into methanol and hydrocarbons. However, the scope of technologies for converting CO₂ into fine chemicals *via* direct insertion into C-H bonds has been somewhat limited.

In this context, coinage metal-based catalysts have primarily been reported to convert arenes, heteroarenes, and terminal alkynes directly to their corresponding carboxylic acids.⁹⁻¹⁶ The C-H carboxylation of terminal alkynes with CO₂ yields propiolic acids, valuable intermediates for the chemical and pharmaceutical industries.¹⁷⁻¹⁹ Although alkyne carboxylation reactions can occur without metals at high temperatures or under ambient conditions,²⁰⁻²² metal catalysts such as copper or silver still dominate this field of research.²³ The reaction mechanism generally involves coordination of the alkyne to the metal center after initial deprotonation by a base, yielding a metal acetylide that serves as a nucleophile toward CO₂ (Scheme 1).²⁴ A subsequent reaction with an alkyl halide is often performed *in situ* to convert the metal propiolates into the corresponding esters to (i) avoid the dissociation of the carboxylic acids at high temperatures and (ii) render the carboxylation irreversible against the competitive decarboxylation reaction.



Scheme 1 Metal-catalyzed C-H carboxylation and esterification with CO₂.

^aDepartment of Chemistry, Oklahoma State University, Stillwater, Oklahoma, 74078, USA. E-mail: tahsini@okstate.edu

^bManchester Institute of Biotechnology, The University of Manchester, 131 Princess Street, Manchester M1 7DN, UK

^cDepartment of Chemical Engineering, The University of Manchester, Oxford Road, Manchester M13 9PL, UK




In the 2010s, several groups reported the application of molecular copper catalysts in the direct carboxylation of terminal alkynes with CO_2 .^{1,3,25–28} The copper(I) centers in these complexes were supported by 1,10-phenanthroline, phosphine, and N-heterocyclic carbene (NHC) ligands, with the NHC present in three out of five reported examples. Recently, copper complexes supported by azothioformamide (ATF) ligands were reported as catalysts for the carboxylation of terminal alkynes.²⁹ Despite the use of different ligand platforms, the existing catalysts perform through similar CO_2 and alkyne activation steps.

Previous studies have shown that the $[\text{Cu}(\text{NHC})(\text{Base})]$ (Base = OH, O^tBu , etc) is the active form of all complexes, wherein copper(I) is bound to a monodentate NHC ligand.^{10,11} The species is readily formed, *in situ* or isolated, through the displacement of the halide anion trans to NHC in the structure of $[\text{Cu}(\text{NHC})(\text{X})]$ complexes. Following the Brønsted–Lowry framework, the $[\text{Cu}(\text{NHC})(\text{Base})]$ species can only activate and carboxylate the C–H bonds of the substrates that are more acidic than the catalyst center. This explains the low reactivity of $[\text{Cu}(\text{IPr})(\text{OH})]$ (IPr = 1,3-bis(diisopropyl)phenylimidazol-2-ylidene) complex ($\text{p}K_{\text{a}}^{\text{DMSO}} = 27.7$)¹¹ in the direct carboxylation of terminal alkynes ($\text{p}K_{\text{a}} \sim 28.8$).³⁰ Previously, it was shown that the reaction can be performed effectively only under high CO_2 pressure (1.5 MPa).²⁷

Interestingly, switching the coordination environment of copper from monodentate NHC to polydentate NHC ligands improved the catalyst reactivity, such that the $\text{P}(\text{NHC})_{0.5}(\text{NHC-Cu})_{0.5}$ complex could carboxylate terminal alkynes under atmospheric pressure of CO_2 . The proposed reaction mechanism involved internal activation of CO_2 by the free NHC arm of the ligand.¹³ Later, the carboxylation mechanism was investigated by theoretical studies of a copper complex containing a pincer bis-NHC ligand as a simpler model. The computational data showed that the most favorable pathway for carboxylation involves activation of CO_2 by a free NHC arm, followed by chelation of the metal by the carboxylated bis-NHC ligand.³¹ Despite using a reasonably similar ligand, the calculated structure of the Cu-CNC complex reported in the work is quite distinct from those in our study, suggesting a potentially different reaction mechanism (*vide infra*).

The 2,6-dimethylpyridyl-linked bis-NHC ligands resemble the lutidine-derived PNP platforms that have been intensely investigated in catalysis. An essential feature of the PNP-containing catalysts is the “non-innocent” behavior of the ligands that can assist the transition metal in activating the substrates. This mechanism, discovered by Milstein,³² is referred to as metal–ligand cooperation (MLC) and operates through the ligand’s dearomatization/aromatization process. The MLC was demonstrated for numerous TM-PNP complexes (TM = Ru, Fe, Co, Rh, Ir, Ni, Pd, Pt, and Re), with Ru, Fe, and Re systems serving as versatile catalysts for hydrogenation, dehydrogenation, and, more recently, CO_2 -derived carbonylation.^{33–35} Additionally, several Cu-PNP systems were reported to exhibit electrophilic addition reactivity toward thiols and methyl triflate *via* a dearomatization/aromatization mechanism on a stoichiometric scale. However, the high

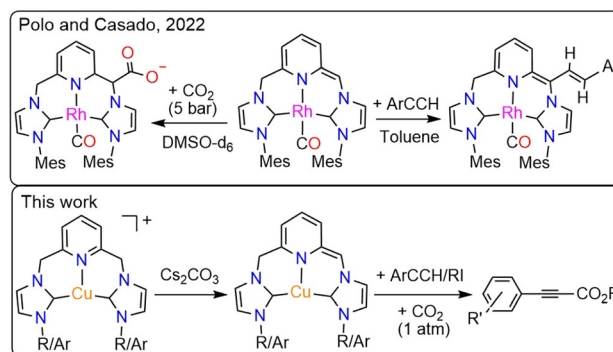

Scheme 2 The reported CO_2 and alkyne activation by a dearomatized Rh-CNC complex and the present work, describing the direct carboxylation of alkynes using Cu-CNC complexes.

solubility of the dearomatized species precluded crystallographic characterization.^{36,37} The use of MLC in activating substrates, particularly dihydrogen, was recently extended to lutidine-derived bis-NHC systems, as phosphine rivals, and several Ru-CNC complexes with pronounced reactivity were reported.^{38,39} Interestingly, the catalytic activity of the Ru-CNC complexes in CO_2 hydrogenation was strikingly lower than that of their Ru-PNP counterpart. Recently, a dearomatized Rh-CNC complex bearing mesityl wingtips was synthesized and characterized crystallographically,⁴⁰ and its reaction with CO_2 and aryl alkynes was examined individually under stoichiometric conditions (Scheme 2).⁴¹ To date, no reports have been published on the carboxylation activity of this or any other TM-CNC complex, which requires simultaneous exposure to both terminal alkynes and CO_2 either stoichiometrically or catalytically. Understanding the fundamental differences between PNP- and CNC-based systems is essential for developing more effective catalysts.

Our group has developed several copper complexes containing 2,6-dimethylpyridyl-linked bis-NHC (CNC) ligands,^{42,43} Herein, we report the use of some of these complexes and new Cu-CNC^{Ar} (Ar = Mes, Dipp) systems as catalysts for the direct carboxylation of terminal alkynes with CO_2 under atmospheric and sub-atmospheric pressures. We also report detailed mechanistic studies of the carboxylation reaction using multiple spectroscopic methods and DFT. This study presents the first spectroscopic and crystallographic characterization of a dearomatized Cu-CNC complex, as well as the role of MLC in the direct carboxylation of terminal alkynes, distinguishing it from previously reported Rh- and Ru-CNC analogs.^{40,44,45}

Results and discussion

Synthesis of the Cu-CNC complexes

2,6-Dimethylpyridyl-linked bis-imidazolium salts of ligands **L1**–**L5** were prepared according to published procedures (Fig. 1).^{42,43} The 2-(4-trifluoromethylaryl)-1-*H* imidazole precursor was synthesized through a Ullman-type C–N coupling reaction catalyzed by the $[\text{Cu}(\text{I}^t\text{Pr}^{\text{C}^{\text{N}}\text{C}})]\text{PF}_6$ complex.⁴⁶ The new imidazolium salts, **L3.2HBr** and **L4.2HBr**, were characterized by ^1H



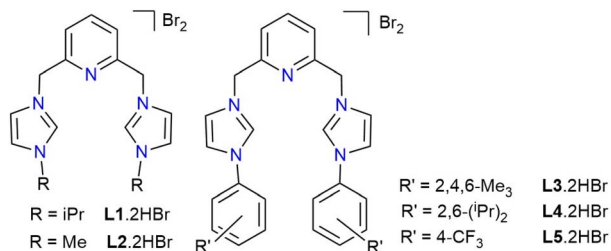


Fig. 1 The pincer CNC^R and CNC^{Ar} ligand precursors, R = *i*Pr (L1.2HBr), Me (L2.2HBr), Ar = Mes (L3.2HBr), Dipp (L4.2HBr), and *p*-CF₃Ar (L5.2HBr).

and ¹³C NMR spectroscopy in DMSO-*d*₆ and elemental analysis. The corresponding Cu-CNC complexes were prepared at room temperature by reacting [Cu(CH₃CN)₄PF₆] with the *in situ* generated CNC ligand through either the method of subsequent addition or combining all solid reactants.⁴³ The new copper complexes, [Cu(IMes^{C^NC})]PF₆ ([Cu-L3]PF₆) and [Cu(I-Dipp^{C^NC})]PF₆ ([Cu-L4]PF₆), were characterized by NMR spectroscopy, elemental analysis, and X-ray crystallography. In addition, the [Cu-L1]BARf and [Cu-L3]BARf complexes were synthesized as more soluble derivatives for mechanism studies and were characterized by NMR spectroscopy and elemental analysis. The pattern of the ¹H and ¹³C{¹H} NMR spectra of these complexes in CD₃CN resembles that of their analogs with alkyl and para-substituted aryl wingtips.^{42,43} The fluxional processes relating both arms of the pincer ligand under ambient conditions lead to sharp singlets for the methylene linkers in the ¹H NMR spectra of these complexes. It was previously shown that the conformational exchanges at the pyridinic hydrogens of the Cu-CNC complexes occur too rapidly to be detected by variable-temperature (VT) NMR spectroscopy, even at 193 K.⁴³

X-ray crystallography of Cu-CNC complexes

Single crystals of complexes [Cu-L3]PF₆ and [Cu-L4]PF₆ were obtained at room temperature through the slow diffusion of diethyl ether into a solution of these complexes in acetonitrile. Crystallographic data collection parameters and selected bond distances and angles are shown in Tables S1 and S2, respectively. In the crystal structure of both complexes, each copper is bound to two NHC rings from the same CNC unit, supporting the chelating coordination mode of the ligand (Fig. 2). The Cu⋯N_{py} distances of 2.221(1) Å in [Cu-L3]⁺ and 2.269(1) Å in [Cu-L4]⁺ resemble those of their analog with bulky *tert*-butyl wingtips,⁴⁷ and are among the shortest distances found for the Cu-CNC complexes with electron-donating alkyl and aryl wingtips.⁴³ The Cu-C_{NHC} bond distances in these complexes are consistent with those reported for other Cu(I)-NHC and Cu(I)-CNC complexes. The C-Cu-C bond angles of 173.97(6)° in [Cu-L3]⁺ and 178.04(6)° in [Cu-L4]⁺ are among the largest values determined for the Cu-CNC complexes of this type. Another notable feature of the Cu-CNC systems is the dihedral angle between the chelate and pyridine rings, which was determined as 162.2(1)° in [Cu-L3]⁺ and 178.8(1)° in [Cu-L4]⁺. These values support

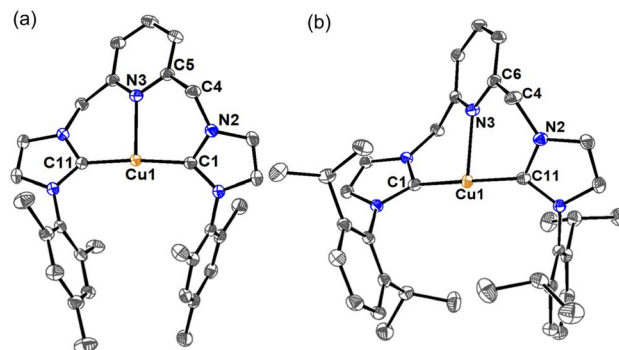


Fig. 2 ORTEP diagrams of (a) [Cu-L3]PF₆ and (b) [Cu-L4]PF₆. Anions, hydrogen atoms, and solvent molecules have been omitted for clarity. Ellipsoids are shown at the 60% probability level.


a nearly coplanar arrangement of the pyridine and NHC rings in the solid-state structure of the complexes. This arrangement is consistent with other Cu-CNC complexes bearing aryl wingtips and is distinct from their alkyl analogs except [Cu(*t*Bu^{C^NC})]PF₆ whose average dihedral angle was 171.5(3)°.

Direct carboxylation of terminal alkynes

Reaction condition screening. Initial transformations of phenylacetylene to propiolic ester were performed using [Cu-L1]PF₆. All reactions were conducted in a sealed Schlenk tube connected to a Schlenk line to maintain 1 atm of CO₂ pressure, as measured by a pressure gauge. The model reaction was initially performed at 80 °C in different solvents, including those that have been optimal solvents with other copper complexes, such as dimethylformamide (DMF),^{13,25} dimethyl sulfoxide (DMSO),²⁹ and dimethylacetamide (DMA).²⁸ Initial screenings were conducted using a 10 mol% loading of [Cu-L1]⁺, with Cs₂CO₃ as the base and iodoethane as the coupling partner.

As shown in Table 1, the highest yield of ethyl 3-phenylpropiolate was obtained in nitrile solvents, including acetonitrile and propionitrile (entries 4 and 5). Reducing the temperature to 60 °C resulted in a significantly lower product yield (entry 6). For the optimized base, two equivalents of Cs₂CO₃ resulted in significantly higher yield (entry 5) than the other inorganic bases tested (entries 7–10). The reaction did not proceed in the presence of KOH (entry 10) due to the base's insolubility.⁴⁸ The reaction time also had a notable effect on the catalyst's performance. The highest product yield was achieved when the reaction was stirred for 12 hours at room temperature, followed by an additional 12 hours at 80 °C (entry 11). Reducing the reaction times at either temperature resulted in a lower yield if the total reaction time was less than 24 hours (entries 13–15). This observation was further supported by the nearly identical yield obtained to that in entry 11 when the reaction mixture was stirred for 1 hour at room temperature and 23 hours at 80 °C (entry 16). While a mixed-temperature state appears essential for optimal catalytic performance, conducting the reaction at room temperature with an extended stirring time of 48 hours also yields the ester product in high yield (entry 17).



Table 1 Screening of reaction conditions with [Cu-L1]PF₆^a


| No. | Solvent | Base (eq.) | Time & temp. (°C) | Yield ^b (%) |
|-----|--------------------|---------------------------------------|----------------------|------------------------|
| 1 | DMSO | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | 56 |
| 2 | DMF | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | 55 |
| 3 | DMA | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | Trace |
| 4 | PrCN | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | 75 |
| 5 | CH ₃ CN | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | 77 |
| 6 | CH ₃ CN | Cs ₂ CO ₃ (2) | 24 h (RT), 24 h (60) | 54 |
| 7 | CH ₃ CN | Cs ₂ CO ₃ (1.1) | 24 h (RT), 24 (80) | 30 |
| 8 | CH ₃ CN | K ₂ CO ₃ (2) | 24 h (RT), 24 h (80) | 11 |
| 9 | CH ₃ CN | K ₃ PO ₄ (2) | 24 h (RT), 24 h (80) | 63 |
| 10 | CH ₃ CN | KOH (2) | 24 h (RT), 24 h (80) | 0 |
| 11 | CH ₃ CN | Cs ₂ CO ₃ (2) | 12 h (RT), 12 h (80) | 88 (48) ^c |
| 12 | CH ₃ CN | Cs ₂ CO ₃ (2) | 12 h (RT), 12 h (80) | 82 ^d |
| 13 | CH ₃ CN | Cs ₂ CO ₃ (2) | 9 h (RT), 9 (80) | 80 |
| 14 | CH ₃ CN | Cs ₂ CO ₃ (2) | 6 h (RT), 6 h (80) | 75 |
| 15 | CH ₃ CN | Cs ₂ CO ₃ (2) | 3 h (RT), 3 h (80) | 69 |
| 16 | CH ₃ CN | Cs ₂ CO ₃ (2) | 1 h (RT), 23 h (80) | 86 |
| 17 | CH ₃ CN | Cs ₂ CO ₃ (2) | 48 h (RT) | 67 |
| 18 | CH ₃ CN | Cs ₂ CO ₃ (2) | 12 h (RT), 12 h (80) | 0 ^e |

^a Reaction conditions: phenylacetylene (0.68 mmol), [Cu-L1]PF₆ (10 mol%), iodoethane (2.0 mmol), base, solvent (5 mL), CO₂ (1 atm).

^b Isolated yields. ^c The yield in the absence of iodoethane. ^d The isolated yield obtained using CO₂ (0.5 atm). ^e The reaction was performed under an Ar atmosphere.

Furthermore, performing the reaction without iodoethane afforded the carboxylic acid at 48% yield (entry 11). The reduced yield of acid compared to the corresponding ester is linked to the instability of propiolic acid derivatives at elevated temperatures. To further improve catalyst performance in the model carboxylation reaction, the concentrations of all reactants were doubled, resulting in a notable increase in the ester product yield at catalyst loadings as low as 2.5 mol% (Fig. S1, SI). In addition, a control experiment was conducted under argon to verify that the carboxylate group originates from CO₂ rather than Cs₂CO₃, yielding no detectable product (entry 18).

Copper catalyst screening. The performance of several Cu-CNC complexes as catalysts was examined in the direct carboxylation of phenylacetylene under the established optimal conditions (Table 2). For comparison, the reaction was also conducted without any copper catalyst (entry 1) and with I^tPr^{C[^]N[^]C}.2HBr salt as the catalyst and source of free NHC (entry 2). While there have been reports suggesting that commercial Cs₂CO₃ can carboxylate terminal alkynes under high CO₂ pressure and elevated temperatures,^{15,20} our experiments using optimized conditions without a copper source yielded no detectable products (entry 1). According to the data in Table 2, the highest yields of propiolate were obtained with [Cu-L3]⁺ and [Cu-L5]⁺ complexes containing the mesityl (Mes) and para-CF₃ aryl wingtips, respectively (entries 6 and 8). In contrast, [Cu-L4]⁺, containing the bulky diisopropylphenyl (Dipp) wingtips, provided the lowest carboxylation yield among the Cu-CNC complexes (entry 7). A practical

Table 2 Screening of Cu(I) catalysts for direct carboxylation of phenylacetylene^a

| Entry | Catalyst | Yield ^b (%) |
|-------|---|------------------------|
| 1 | No copper | 0 ^c |
| 2 | I ^t Pr ^{C[^]N[^]C} .2HBr | 11 |
| 3 | [Cu(I ^t Pr ^{C[^]N[^]C})]PF ₆ , [Cu-L1]PF ₆ | 88 |
| 4 | [Cu(I ^t Pr ^{C[^]N[^]C})]PF ₆ (<i>in situ</i>) ^d | 83 |
| 5 | [Cu(IME ^{C[^]N[^]C})]PF ₆ , [Cu-L2]PF ₆ | 85 |
| 6 | [Cu(IMes ^{C[^]N[^]C})]PF ₆ , [Cu-L3]PF ₆ | 95 |
| 7 | [Cu(IDipp ^{C[^]N[^]C})]PF ₆ , [Cu-L4]PF ₆ | 64 |
| 8 | [Cu(⁴ -CF ₃ Ar ^{C[^]N[^]C})]PF ₆ , [Cu-L5]PF ₆ | 99 |
| 9 | [Cu(CH ₃ CN) ₄]PF ₆ | 64 |

^a Reaction conditions: phenylacetylene (0.68 mmol), cat. (10 mol%), iodoethane (2.00 mmol), Cs₂CO₃ (1.37 mmol), CH₃CN (5 mL), CO₂ (1 atm). ^b Isolated yields. ^c No copper catalyst. ^d Conditions: Cu(CH₃CN)₄PF₆ (0.068 mmol), I^tPr^{C[^]N[^]C}.2HBr (0.082 mmol), Cs₂CO₃ (1.37 mmol), phenylacetylene (0.68 mmol), iodoethane (2.00 mmol), CH₃CN (5 mL), CO₂ (1 atm).

aspect of the current system is that the Cu-CNC catalysts can be generated *in situ* and still afford a comparable yield (entry 4) to that obtained using an isolated complex (entry 3). The control experiments also indicated that the [Cu(CH₃CN)₄]PF₆ salt could provide the propiolate ester at a reasonable yield under optimal conditions (entry 9).

Substrate scope screening. To investigate the scope of application of the Cu-CNC catalysts, the direct carboxylation of a diverse range of terminal alkynes was examined under optimized conditions using [Cu-L1]⁺. This choice of complex over [Cu-L5]⁺, which provided the highest yield, was made to keep consistency between catalytic reactions and mechanistic studies. As shown in Fig. 3, the ethyl or butyl 2-alkynoates of various alkyl- and aryl-substituted terminal alkynes were obtained in good to excellent yields. Phenylacetylenes containing electron-donating groups, *e.g.* Me, Et, ^tBu, and OEt, were converted to the corresponding alkynoates in good (67%) to excellent (99%) yields. The relatively low yield of ethyl 3-(4-ethylphenyl)propiolate (**4**) could be related to the instability of this product at the reaction temperature since a significant improvement was observed with ⁿBuI as the esterification reagent (**5**). In addition to activated alkynes, electron-withdrawing groups on the *ortho*-, *meta*- or *para*-positions of phenylacetylene were well tolerated and provided good (62%) to excellent (98%) yields. This is important because terminal aromatic alkynes with strong electron-withdrawing substituents, such as 4-nitro or 4-cyano, are the least reactive substrates in carboxylation due to their reduced nucleophilicity.⁴⁹ This feature has led to their absence from the carboxylation studies performed on terminal alkynes in the presence of several copper complexes.^{25,27,50} In some cases, zero product yields have been reported for these derivatives.²⁸ For the 4-halophenylacetylenes, the substrate activity is related to the electronegativity of halogen in the order F >> Cl > Br. Notably, 3-(4-fluorophenyl)propiolate (**8**) presented the highest yield among the para-substituted derivatives. Moreover, the 2-halophenyl acetylenes (**10** and **12**) demonstrated higher reactivity than their para-substituted analogs (**9** and **11**). Interestingly, these trends



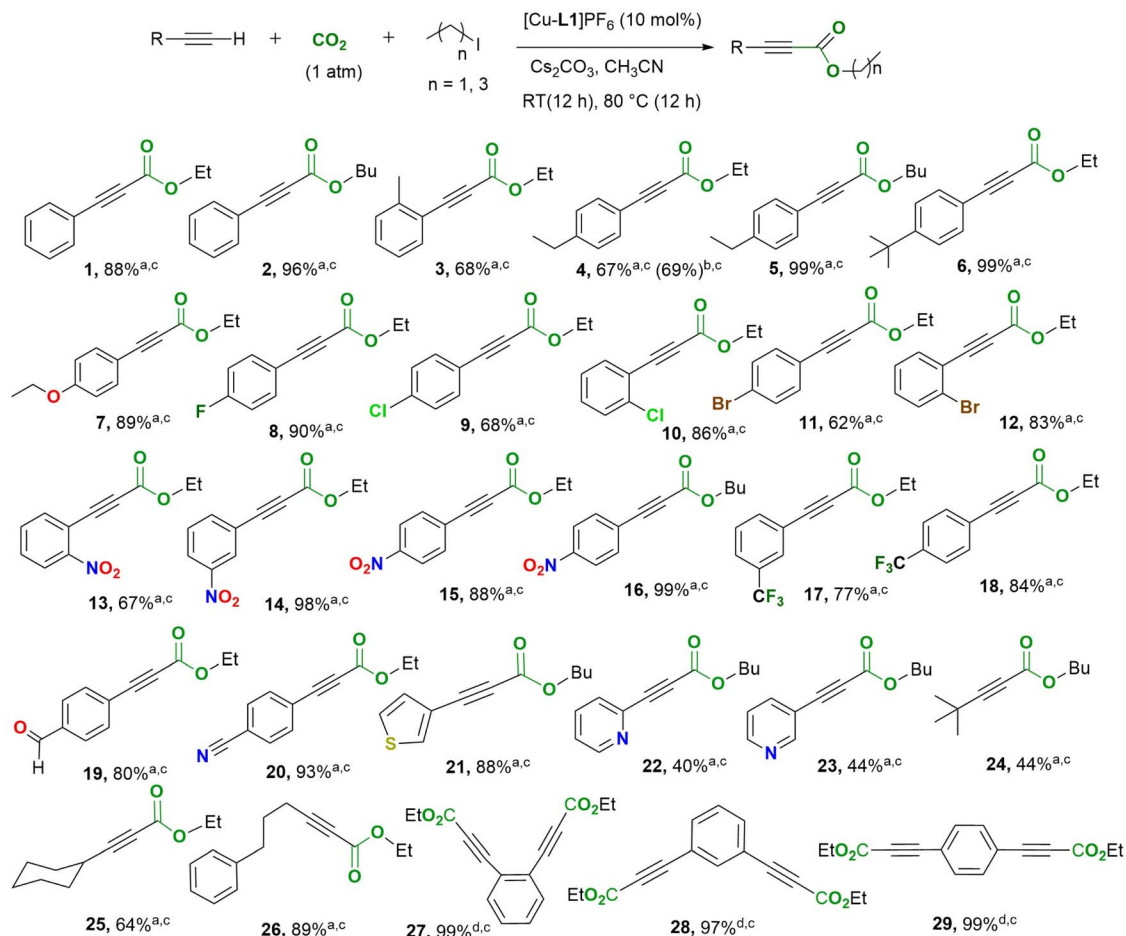


Fig. 3 Direct carboxylation-esterification of terminal alkynes with CO₂ catalyzed by [Cu-L1]PF₆. Reaction conditions include (a) [Cu] (10 mol%), terminal alkyne (1.0 equiv.), Cs₂CO₃ (2.0 equiv.), EtI or ^tBuI (2.9 equiv.), CO₂ (1 atm), CH₃CN (5 mL), 12 h at RT, 12 h at 80 °C. (b) 6 h at RT, 6 h at 80 °C. (c) Isolated yield. (d) [Cu] (10 mol%), terminal alkyne (1.0 equiv.), Cs₂CO₃ (4.0 equiv.), EtI (6.0 equiv.), CO₂ (1 atm), CH₃CN (5 mL), 12 h at RT, 12 h at 80 °C.

have not been observed in other copper systems supported by poly-NHC¹³ or non-NHC ligands,^{29,50} suggesting a different reaction mechanism. The position of the electron-withdrawing group also influences the reactivity of the nitrophenylacetylenes (13–15), with the *meta*-nitro derivative presenting the highest yield of the propiolate product (14). In addition to the aryl terminal alkynes, aliphatic alkynes were also converted efficiently to their corresponding esters at yields ranging from 44% to 89%. The low and moderate yields of 3,3-dimethyl-1-butyne and 1-cyclohexyne, respectively, are attributed to their volatility and/or instability at the reaction temperature (24, 25). In contrast, the less volatile substrates, such as 5-phenyl-1-pentyne, provided decent yields of the corresponding propiolate product (26). Furthermore, substrates bearing a hetero-aromatic ring system were also employed, including 3-ethynyl thiophene, 2-ethynyl pyridine, and 3-ethynyl pyridine. Both ethynyl pyridine derivatives provided relatively low yields (22 and 23), whereas 3-ethynyl thiophene gave a decent yield (21). The poor performance of copper complexes toward basic nitrogen heterocycles was previously observed in CuI/PET₃,²⁸ Cu(IPr)Cl,²⁷ and Cu-ATF systems.²⁹ This could be attributed to

the coordinating ability of nitrogen heterocycles, which slows down catalysis. We also examined the direct carboxylation of double-terminal alkynes under optimized conditions. This assessment revealed the complete conversion of all three di-ethynyl benzene derivatives to their corresponding carboxylate forms (27–29). Attempts to obtain the mono-carboxylate derivative using reduced base concentrations resulted in a mixture of products.

Catalyst performance metrics. To investigate the stability of the copper catalyst and potential deactivation during the reaction cycle, a catalyst recovery method was developed. In this process, the crude mixture from the catalytic reaction underwent multiple hexane triturations to extract the propiolate ester product (83%). The remaining solid was purified through a series of trituration and recrystallization to yield the copper complex in its entirety. The ¹H NMR spectrum of the recovered complex revealed two sets of resonance signals corresponding to [Cu-L1]PF₆ (85%) and another Cu-CNC species (15%) with the same pattern but slightly different chemical shifts (Fig. S2, SI). Despite the difference, the minor copper derivative also contains methylene linkers, which can generate a dearomatized



species upon deprotonation. Reusing the recovered catalyst in its entirety yielded 83% of the corresponding propiolate ester for at least five cycles, confirming the stability of the Cu-CNC complexes under the reaction conditions. Furthermore, tracking the reaction's progress over time indicates a consistent increase in yield, supporting the catalyst's stability in this process (Fig. S3, SI). It is important to note that the catalyst selectively promotes carboxylation without producing any other side products. Furthermore, when evaluating the catalyst's performance under scaled-up conditions (see Fig. S1, SI), a turnover number (TON) of 30.0 and a turnover frequency (TOF) of 1.25 were observed for the [Cu-L1]PF₆ catalyst.

Experimental mechanistic study

Despite the promising application of a handful of Cu-NHC complexes as catalysts in the direct carboxylation of terminal alkynes with CO₂, the reaction mechanisms are still unclear.^{13,27,51} This is partly due to NHC's ambiguous role in these reactions and the limited scope of the available molecular copper catalysts. In the [Cu(NHC)Cl] complexes, wherein NHC is a monodentate ligand, the strong σ -donation of NHC and the lability of the halide trigger the formation of [Cu(NHC)(OH)] as a versatile synthon capable of activating various X-H bonds (X = C, N, O).⁵² A subsequent step involving CO₂ insertion into the Cu-acetylide bond results in the propiolate anion, which can undergo an S_N2 reaction with an alkyl/allyl halide, producing a propiolate ester.⁵³ On the other hand, the carboxylation mechanism with the Cu-poly(NHC) complex is notably different. While the alkynyl C-H bond activation in this complex is similar to that of neutral [Cu(NHC)Cl], CO₂ activation occurs at the nucleophilic site of the free NHC in the structure.³¹ A unique feature of the Cu-CNC complexes in this study is the chelation of copper by the pincer ligand and the *trans*-orientation of the two NHC units. This arrangement disfavors the displacement of a *trans* NHC ligand, avoiding the formation of reactive [Cu(NHC)(X)] (X = Brønsted base) species. In contrast, it enables the formation of other reactive species, which are examined in the following stoichiometric and single-step reactions.

Deprotonation of [CuL1]BARf and [CuL3]BARf complexes with a base. The coordination of lutidine-based pincer ligands to late-transition metals results in acidic methylene linkers that are susceptible to deprotonation by a base, as reported by Milstein.³³ The resulting dearomatized species are highly reactive and are often characterized by spectroscopic methods in solution. The reaction of [Cu-L1]BARf with KO^tBu in a 1 : 20 molar ratio was performed in THF-*d*₈ at room temperature and was monitored by ¹H NMR spectroscopy. The UV-vis studies of the reaction revealed the need for an excess of base to allow the complete formation of the dearomatized complex (*vide infra*). The ¹H NMR spectrum of the dearomatized complex [Cu-L1*], obtained upon mixing the reagents (Fig. 4a) or after 24 h of stirring at room temperature, displayed a drastic change in the position and number of signals compared to [Cu-L1]BARf (Fig. S4, SI). The dearomatization of the pyridine ring is reflected in three distinct aromatic signals corresponding to the

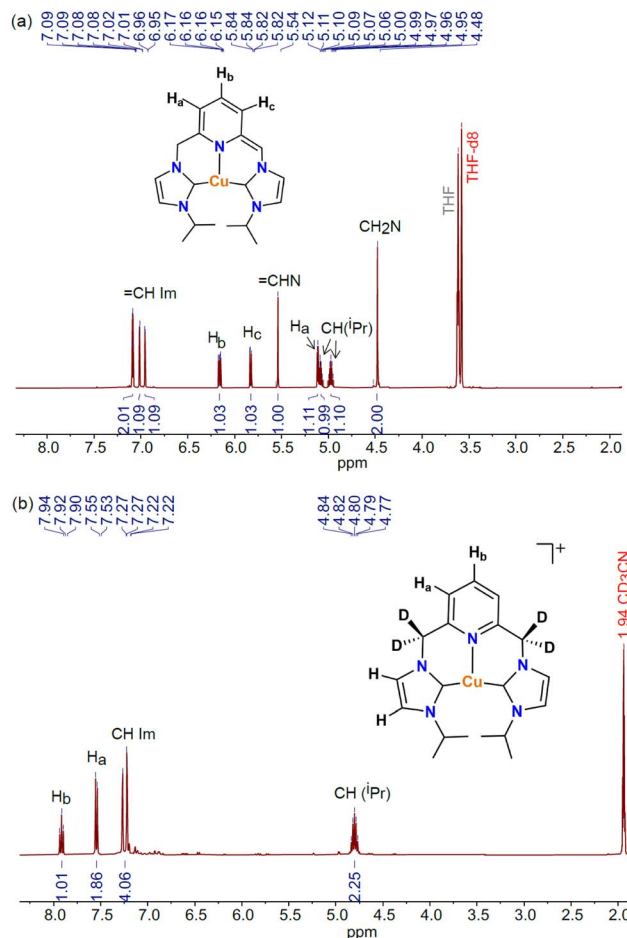


Fig. 4 (a) ¹H NMR spectrum (8.0–2.0 ppm) for [Cu(L1PrC^{AN}C)*], [Cu-L1*], in THF-*d*₈ at 298 K. (b) ¹H NMR spectrum (8.0–2.0 ppm) of the reaction of [Cu-L1]PF₆ (1 equiv.) and Cs₂CO₃ (5 equiv.) in CD₃CN after 24 h stirring at room temperature.

para and *meta* hydrogen atoms that experience a significant upfield shift to 6.16, 5.83, and 5.11 ppm. The methylene group resonances appear at 4.48 ppm as a singlet, a pattern known for copper complexes containing lutidine-based CNC ligands.^{42,43} Furthermore, the =CHN signal of the deprotonated arm was observed as a singlet at 5.54 ppm. Similar resonance signals were also detected for [Cu-L3*] prepared *in situ* through the reaction of [Cu-L3]BARf and KO^tBu (5 equiv.) in THF-*d*₈ (Fig. S5, SI). These key resonances of [Cu-L1*] and [CuL3*] resemble a similar pattern to that reported earlier for the Rh-CNC analog in THF-*d*₈.⁴⁰

While generating the dearomatized species in THF-*d*₈ using excess KO^tBu is imperative for its characterization, understanding its stability and reactivity in acetonitrile is crucial for catalysis. To explore this concept, the [Cu-L1]PF₆ complex was treated with stoichiometric and excess amounts of Cs₂CO₃ in CD₃CN to enable the formation of [Cu-L1*]. The ¹H NMR spectra of reaction mixtures were obtained after 24 hours of stirring at room temperature. As shown in Fig. 4b, the spectrum closely resembles the resonances observed in the initial complex (Fig. S6, SI), but the methylene linkers have entirely



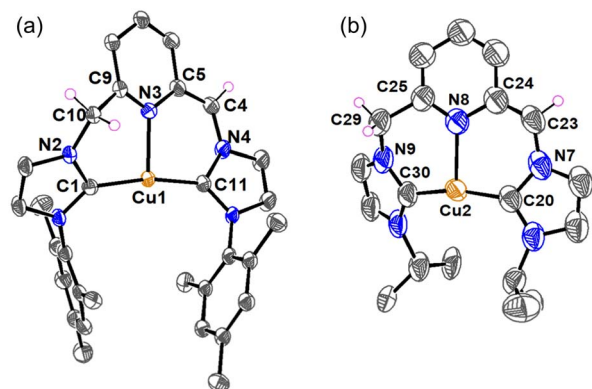


Fig. 5 ORTEP diagrams of (a) [Cu-L3*] and (b) [Cu-L1*]. Hydrogen atoms have been omitted for clarity, except those of the methine and methylene arms. Only one of the crystallographically unique molecules is shown for [Cu-L1*]. The disorder sites for this molecule were omitted for clarity. Ellipsoids are shown at the 60% probability level.

vanished. This result is due to the full deuteration of the CH₂ groups in [Cu-L1]PF₆, as confirmed by a broad peak in the ²H NMR spectrum of the reaction in CD₃CN (Fig. S7, SI). The same phenomenon occurred with a stoichiometric amount of Cs₂CO₃, resulting in the starting complex with fully deuterated methylene linkers ([Cu-L1^D]⁺, Fig. S8, SI). These data highlight the reactive nature of the dearomatized species in acetonitrile.

In addition to spectroscopic characterization, we successfully grew single crystals of [Cu-L3*] and [CuL1*] in a THF solution at -30 °C for X-ray crystallography studies. The molecular structures of the complexes are shown in Fig. 5, along with the main bond angles and bond distances in Table S2. A set of relevant bond distances and angles in the aromatized and dearomatized complexes is also given in Table 3 for comparison. While the coordination environment and the Cu-C_{NHC} bond distances of [Cu-L3*] and [Cu-L1*] resemble those of [Cu-L3]⁺ and [Cu-L1]⁺, respectively, the Cu-N_{py} distances are

Table 3 Significant bond distances and angles in the [Cu-L]PF₆ and [Cu-L*]

| Complex | Bonds | Distances (Å)/angles (°) | Ref. |
|------------------------|------------------|--------------------------|-----------|
| [Cu-L1]PF ₆ | Cu(1)-N(1) | 2.294(1) | 42 |
| | C(5)-C(4) | 1.510(2) | |
| | C(9)-C(8)-N(3) | 114.5(1) | |
| [Cu-L3]PF ₆ | Cu(1)-N(3) | 2.221(1) | This work |
| | C(5)-C(4) | 1.510(2) | |
| | C(5)-C(4)-N(2) | 115.0(1) | |
| | C(23)-C(24) | 1.35(3) | |
| [Cu-L1*] | Cu(2)-N(8) | 2.10(1) | This work |
| | C(23)-C(24) | 1.35(3) | |
| | C(25)-C(29) | 1.55(2) | |
| | C(24)-C(23)-N(7) | 129(2) | |
| | C(25)-C(29)-N(9) | 114(1) | |
| [Cu-L3*] | Cu(1)-N(3) | 2.095(4) | This work |
| | C(5)-C(4) | 1.36(1) | |
| | C(9)-C(10) | 1.52(2) | |
| | C(5)-C(4)-N(4) | 128(1) | |
| | C(9)-C(10)-N(2) | 113(1) | |

significantly shorter, due to an increase in the donor character of the pyridinic nitrogen. Furthermore, the increase in the C(5)-C(4)-N(4) bond angle from 115.0(1)° in [Cu-L3]⁺ to 128(1)° in [Cu-L3*] and the decrease of the C(5)-C(4) bond distance from 1.512(2) Å in [Cu-L3]⁺ to 1.36(1) Å in [Cu-L3*] are noticeable. The same trend was observed for the C(24)-C(23)-N(7) bond angle and the C(23)-C(24) bond length in [Cu-L1*] compared to their counterparts in [Cu-L1]⁺. Additionally, the alternated bond lengths of the pyridyl groups in [Cu-L3*] and [Cu-L1*] indicate the disruption of the aromaticity within the ring (Table S2, SI). Due to the limited number of crystallographically characterized dearomatized TM-CNC, the structural data for the current [Cu-L*] derivatives can be compared with the Rh-CNC counterpart, the only previously reported example before our work.⁴⁰ Although the coordination geometry differs and a π-acceptor CO is present on Rh, the essential structural characteristics of the dearomatized Cu-CNC complexes—such as the shorter metal-N_{py} distance, the shorter C-C bond, and the larger C-C-N bond angle of the methine linker—are consistent with those observed in the rhodium counterpart.

Next, the formation and stability profile of the dearomatized species was further investigated using UV-vis spectroscopy at low temperatures. The reaction of [Cu-L1]BARF with excess KO^tBu in THF produces a dark red chromophore with ligand-centered absorption bands around 280–350 nm and four absorption maximum wavelengths (λ_{max}) at 423 nm (ε = 7.2 × 10³ M⁻¹ cm⁻¹), 475 nm (ε = 2.7 × 10³ M⁻¹ cm⁻¹), 505 nm (ε = 2.0 × 10³ M⁻¹ cm⁻¹), and 539 nm (ε = 9.0 × 10² M⁻¹ cm⁻¹). The ε values of [Cu-L1*] were determined by spectral titration of [Cu-L1]BARF with base in THF at 223 K (Fig. S9, SI). We also attempted to clarify the nature of electronic transitions in the UV-vis spectrum using time-dependent density functional theory (TD-DFT). The calculated spectrum resembled prominent features similar to those found experimentally; however, the positions and numbers of absorption bands differed slightly (Fig. S10, SI). This difference is attributed to the solvent effects and interactions with other ions present in solution, including excess base. According to the calculations, the absorbance at 340 nm is primarily ligand-to-ligand charge-transfer (LLCT), while the peak at 423 nm is a hybrid of metal-to-ligand charge-transfer (MLCT) and LLCT transitions. Furthermore, the absorption band at 505 nm originates primarily from ligand-to-metal charge-transfer (LMCT) transitions.

Since the formation of the dearomatized complex requires excess base amounts, an equilibrium between the [Cu-L1]⁺ and [Cu-L1*] species is postulated in solution (eqn (1)). A spectral titration of [Cu-L1]⁺ with KO^tBu was performed in THF at 193 K to determine the deprotonation constant (K_{dp}) using eqn (2). This equation is easily converted to eqn (3), where [CuL1]₀ and [KO^tBu]₀ are initial concentrations of [Cu-L1]⁺ and base, respectively, and x is the equilibrium concentration of [Cu-L1*] calculated using Beer's law and the absorbance change at 505 nm due to [Cu-L1*] (Fig. 6). The K_{dp} value is then determined from the inverse of the slope of a linear plot of (([CuL1]₀ - x)/x) versus 1/([KO^tBu]₀ - x) to be 8.8 × 10 M⁻¹.



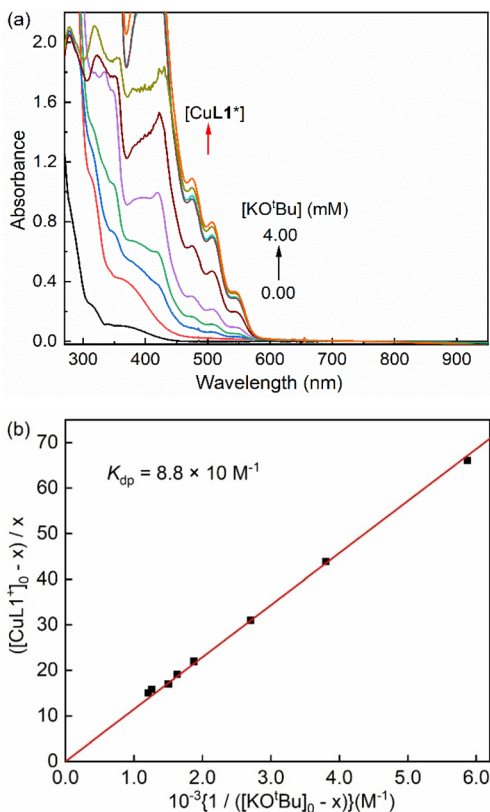


Fig. 6 (a) UV-vis spectral changes of [Cu-L1]BARF (0.50 mM) in the presence of KOtBu (0.0–4.0 mM) in THF at 193 K. (b) Plot of $([\text{CuL1}^+]_0 - x)/x$ versus $1/([\text{KOtBu}]_0 - x)$ to determine the deprotonation constant of $[\text{CuL1}^+]$ upon addition of KOtBu (0.0–4.0 mM) into the solution of $[\text{CuL1}^+]$ (0.40 mM) in THF at 193 K.

$$K_{\text{dp}} = [\text{CuL1}^*]/[\text{CuL1}^+][\text{KOtBu}] \quad (2)$$

$$([\text{CuL1}^+]_0 - x)/x = K_{\text{dp}}^{-1} (1/([\text{KOtBu}]_0 - x)) \quad (3)$$

In the next step, the temperature dependence of K_{dp} was examined (Fig. S11, SI), and the van't Hoff plot afforded the enthalpy of formation ($\Delta H = -2.3 \pm 0.2 \text{ kcal mol}^{-1}$) and the entropy of formation ($\Delta S = -3.2 \pm 0.7 \text{ cal K}^{-1} \text{ mol}^{-1}$) for the dearomatized complex $[\text{CuL1}^*]$ in THF (Fig. S12, SI).

In addition to the formation constant of $[\text{Cu-L1}^*]$, the dynamics of its reaction with the base were examined by UV-vis spectroscopy at 223 K. Fig. 7 shows the spectral changes corresponding to the formation of $[\text{Cu-L1}^*]$ (0.10 mM) in the presence of 0.5 mM KOtBu. At this temperature, $[\text{CuL1}^+]$ is fully converted to the dearomatized complex, as shown by the plateaued time profile within 160 seconds. The species remains reasonably stable at this temperature in the absence of air and moisture. The formation rate of $[\text{Cu-L1}^*]$ follows pseudo-first-order kinetics in THF at 223 K with a pseudo-first-order rate constant (k_{obs}) of $2.3 \times 10^{-2} \text{ s}^{-1}$ and a second-order rate constant (k_2) of $4.6 \times 10 \text{ M}^{-1} \text{ s}^{-1}$, considering the concentration of the base. The formation of this species was also performed under a pseudo-first-order condition at 193 K, where a pseudo-

first-order rate constant of $8.4 \times 10^{-3} \text{ s}^{-1}$ and a second-order rate constant of $8.4 \text{ M}^{-1} \text{ s}^{-1}$ were determined (Fig. S13, SI). The Eyring analysis of the rate constants at 223 K and 193 K (eqn (4)) provided an estimate of the activation enthalpy ($\Delta H^\ddagger = 4.43 \pm 0.1 \text{ kcal mol}^{-1}$) and activation entropy ($\Delta S^\ddagger = -30.5 \pm 2 \text{ cal K}^{-1} \text{ mol}^{-1}$). The relatively small value of ΔH^\ddagger , and the negative value of ΔS^\ddagger is usually consistent with an associative mechanism or an entropy-governed process.^{54,55} These values are comparable to those obtained for the photochemical carbonylation of benzene by a dearomatized Rh-PNP species, which follows an associative mechanism.³⁵ Currently, no documented activation parameters have been reported for similar CNC-based dearomatized species in the literature.

$$\ln \frac{k}{T} = -\frac{\Delta H^\ddagger}{R} \left(\frac{1}{T} \right) + \ln \frac{k_{\text{B}}}{h} + \frac{\Delta S^\ddagger}{R} \quad (4)$$

Reactivity of [Cu-L1]PF₆ with phenylacetylene in the presence of the base. To develop an understanding of the species involved in the carboxylation mechanism, the reaction of $[\text{Cu-L1}]\text{PF}_6$ and phenylacetylene was examined in the presence of a base. Initially, it is assumed that the reaction between phenylacetylene and the base takes precedence over the formation of the dearomatized species. To investigate this idea, the copper complex was treated with one equivalent of sodium phenylacetylide (NaPA) in CD₃CN. The reaction was monitored by ¹H NMR spectroscopy both at the mixing time and after 24 hours of stirring at room temperature, revealing the formation of a new species (Fig. 8). This species is characterized by two olefinic hydrogen signals at 6.93 and 6.47 ppm, which correlate with signals at 121.46 and 120.24 ppm in the ¹³C{¹H} NMR spectrum, respectively (Fig. S14 and S16, SI). Additionally, a set of aromatic signals ranging from 7.07 to 7.28 ppm is observed, which corresponds approximately to a hydrogen ratio of 4 : 1. This pattern somewhat resembles that observed for a Rh-styrenyl complex, which is formed as an addition product of phenylacetylene on the dearomatized Rh-CNC complex.⁴¹ In contrast to the rhodium analog, the Cu-styrenyl species (**Cu-S**) is highly symmetrical, as evident from a single set of methine hydrogens (CH_{iPr}) and the CHN linkers, as well as an integrated ratio of 1 : 1 : 1 for the CH(ⁱPr) : CHN(linker) : olefinic hydrogens. Moreover, the presence of a singlet at $\delta(^{13}\text{C})$ 187.67 ppm for the two carbenic NCN atoms is consistent with the symmetrical substitution of styrene units in this complex (Fig. S16, SI). While the initial **Cu-S** species is expected to be dearomatized, it readily undergoes saturation in acetonitrile, as indicated by the presence of CHN linkers at 5.02 ppm (Fig. S14, SI). In addition to signals from the **Cu-S** species, a set of low-intensity resonances was observed in the ¹H NMR spectrum at 6.27, 6.09, 5.95, and 5.57 ppm. These features, which are only visible in the spectrum within the mixing time of the reaction, resemble those in the spectrum of $[\text{Cu-L1}^*]$ in THF-*d*₈ (Fig. 4a). This is significant as it demonstrates the deprotonation of the methylene linkers of $[\text{Cu-L1}^+]$ by the acetylide anion. Moreover, the low signal intensity indicates the involvement of the dearomatized species in the formation of the **Cu-S** complex, as previously shown for the Rh-CNC systems. Extending the reaction time to 24 hours



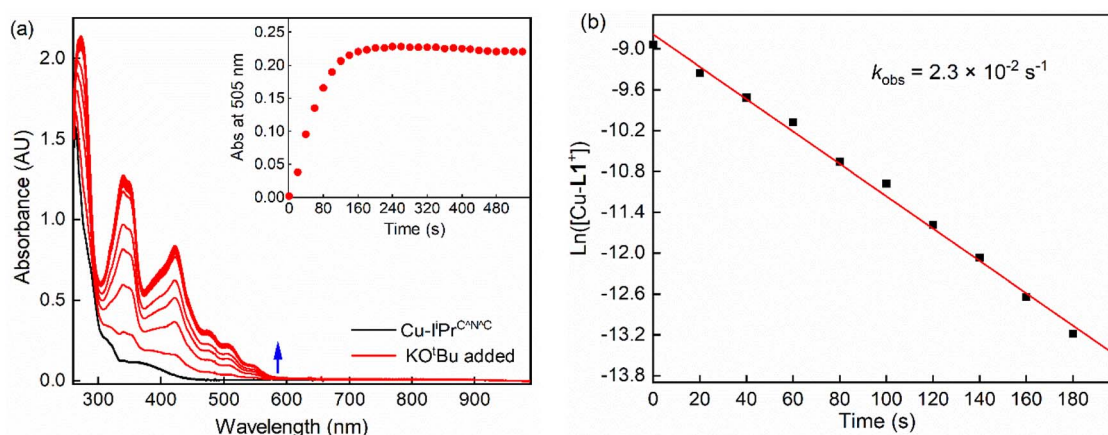


Fig. 7 (a) UV-vis spectral changes observed in the deprotonation of $[\text{Cu-L1}]\text{BARF}$ (0.10 mM) with KO^tBu (0.50 mM) in THF at 223 K. The inset shows the time profile of the absorbance at 505 nm due to $[\text{Cu-L1}^*]$. (b) The first-order plot of $[\text{Cu-L1}^*]$ formation under these conditions.

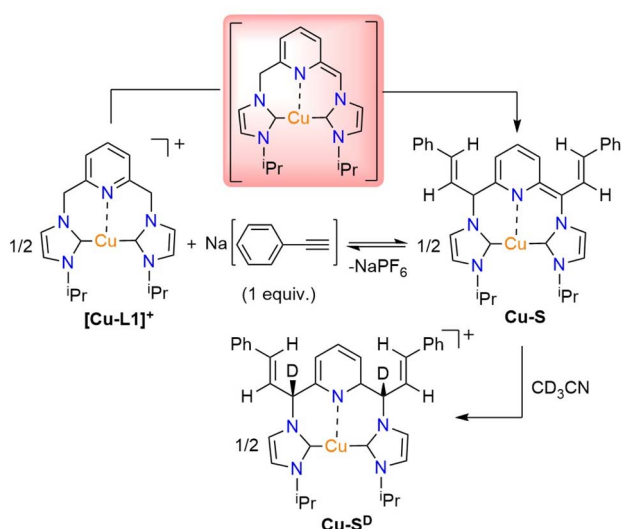


Fig. 8 The Cu-styrenyl complex (**Cu-S**) formed from the reaction of $[\text{Cu-L1}]\text{PF}_6$ and one equivalent of NaPA.

afforded the **Cu-S^D** complex with fully deuterated methine linkers as the primary product, as shown by the complete absence of these signals in the ^1H NMR spectrum (Fig. S15a, SI). The results were further confirmed by the ^2H NMR analysis of the reaction mixture in CD_3CN (Fig. S15b, SI). The lack of detectable pyridine and NHC backbone signals in the ^1H NMR spectrum is attributed to rapid hydrogen–deuterium exchange, which was not detectable by ^2H NMR at room temperature. Remarkably, the formation of **Cu-S** species appears to be reversible owing to the presence of NaPA resonances in the ^1H NMR spectrum either upon mixing or after 24 h of stirring. This was further supported in the CO_2 addition process, *vide infra*.

Increasing the amount of NaPA to five equivalents in the reaction with $[\text{Cu-L1}]^+$ resulted in a different product, as evident from the absence of two olefinic hydrogens in the ^1H NMR spectrum after 24 hours of stirring (Fig. S17a, SI). A set of aromatic resonances (7.08–7.25 ppm) at a hydrogen ratio of 2 :

2 : 1 is also distinct from those of the styrenyl groups of the **Cu-S** species. The signals' pattern and relative integration resemble those of copper-acetylide complexes bearing NHC ligands prepared by others and by us (Fig. S18a, SI).^{56,57} The presence of acetylenic carbon signals at δ 94.19 and 83.68 ppm in the ^{13}C $\{^1\text{H}\}$ NMR spectrum of **Cu-A** further supports this assignment (Fig. S18b, SI). Furthermore, the extensive deuterium exchange of the methylene linkers, the CH group of the isopropyl wing-tips, and the pyridyl hydrogens support an initial formation of a dearomatized **Cu-A** species (Fig. 9). This theory was further supported by the appearance of resonance signals at 4.82, 5.31, and 7.59 ppm in the ^2H NMR spectrum of the reaction, which correspond to the absent hydrogen groups in the ^1H NMR spectrum (Fig. S17b, SI).

To evaluate the formation speed of **Cu-A**, the reaction between $[\text{Cu-L1}]^+$ and NaPA (5 equiv.) was examined during the mixing time. The ^1H NMR spectrum of the reaction confirmed the complete formation of the species and less deuteration. Additionally, the **Cu-S** peaks, including the methine linkers, isopropyl CH, and olefinic hydrogens, were observed (Fig. S19,

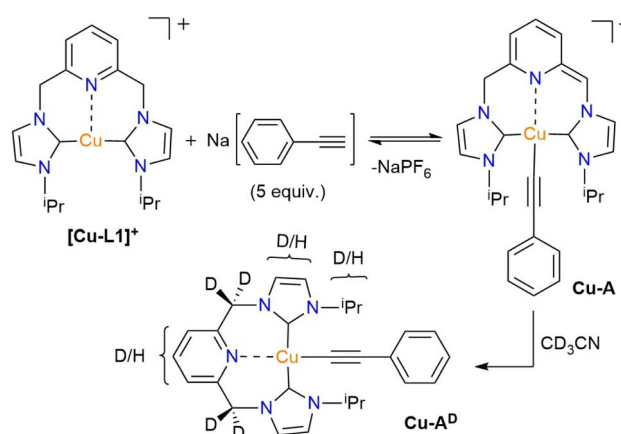


Fig. 9 The Cu-acetylide complex (**Cu-A**) from reacting $[\text{Cu-L1}]\text{PF}_6$ with excess NaPA.



SI). While these signals are much weaker than those of the **Cu-A** species, their presence suggests a possible transformation of the **Cu-S** to **Cu-A** in the presence of excess NaPA. Although the mechanism of this transformation remains to be clarified, it provides a valuable approach for utilizing the nucleophilic character of the dearomatized species beyond stoichiometric conditions. The Cu-acetylide formation is significant for catalysis, given its role as an active intermediate in the copper-catalyzed carboxylation of sp C–H bonds.⁵⁸

To shed light on the **Cu-S** to **Cu-A** conversion, the reaction of $[\text{Cu-L1}]^+$ and NaPA (1 equiv.) was examined at both room and high temperatures. The ^1H NMR spectrum of the reaction within one hour of mixing at room temperature revealed the resonance signals of **Cu-S** (Fig. S20a, SI). Stirring this mixture at 80 °C for 12 h yielded the **Cu-A** species (Fig. S20b, SI), as indicated by NMR signals similar to those observed in the presence of excess NaPA. Slight broadening of the peaks is related to the dissociation of the acetylide anion from copper at high temperatures and to the reduced solubility of the acetylide salt. The experiment was repeated with $[\text{Cu-L3}]\text{PF}_6$ complex and NaPA (1 equiv.), resulting in the formation of **Cu-S** species initially (Fig. S21, SI). Storing the solution under an inert atmosphere overnight resulted in yellow/orange crystals, which were collected and characterized by X-ray crystallography. As shown in the ORTEP diagram (Fig. S22, SI), the acetylide anion is directly bound to copper along with two NHC units from each of the two **L3** ligands in the asymmetric unit. While the coordination mode of **L3** is bridging for the **Cu-A** in the solid state, this could change in solution to the chelating mode, as was shown previously for the pincer CNC ligands bearing aryl wingtips.⁴³

Despite the feasibility of forming the **L1**-supported **Cu-S** and **Cu-A** species in solution, isolating these species for further characterization by X-ray crystallography and elemental analysis has proven somewhat challenging. The solid collected after removing solvent from the **Cu-S^D** solution contains both **Cu-A^D** and **Cu-S^D** species at a mole ratio of approximately 35% to 65%, as indicated by the ^1H NMR spectrum in CD_3CN (Fig. S23, SI). Further work-up of the crude solid through THF trituration resulted in 82% of the $[\text{Cu-L1}]^+$ along with 18% of **Cu-S^H** species (Fig. S23, SI). In the absence of X-ray data, the DFT-optimized structures of **Cu-S** and **Cu-A** were obtained, thereby supporting the proposed intermediates from NMR spectroscopy (Fig. 10).

In the next step, $[\text{Cu-L1}]\text{PF}_6$, base, and alkyne were combined and reacted in a single step. This setup more closely resembles that of the catalytic reaction. The initial study involved a stoichiometric 1 : 1 : 1 ratio of the reagents, mixed as a solid, and stirred for 24 hours at room temperature in CD_3CN . The ^1H NMR spectrum of the reaction mixture revealed two sets of methine and methylene linker resonances corresponding to the **Cu-A^H** (27%) and **Cu-S^H** (73%) species, respectively (Fig. S24a, SI). The resonance signals of the starting complex in the spectrum indicate the existence of an equilibrium between $[\text{Cu-L1}]^+$ and the products (eq (5)). Furthermore, the NMR spectrum showed an acidic signal for phenylacetylene at 3.39 ppm, with a 70 : 30 ratio of phenylacetylene to the acetylide salt, supporting the priority of deprotonating the methylene linkers over deprotonating the alkyne.


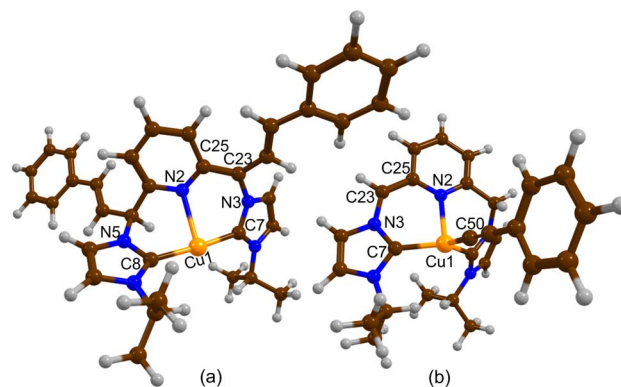


Fig. 10 Optimized structure of (a) **Cu-S** and (b) **Cu-A** calculated by DFT UB3LYP-GD3BJ containing LANL2TZ⁺ (+ECP) on Cu and 6-311+G* on the rest of the atoms. Selected distances (Å) and angles (°): **Cu-S**; Cu(1)–N(2) = 2.415, Cu(1)–C(7) = 1.925, Cu(1)–C(8) = 1.931, C(23)–C(24) = 1.427, C(31)–C(32) = 1.527, C(24)–C(23)–N(3) = 118, C(31)–C(33)–N(5) = 108. **Cu-A**; Cu(1)–N(2) = 2.341, Cu(1)–C(7) = 2.005, Cu(1)–C(8) = 2.043, Cu(1)–C(50) = 1.965, C(23)–C(25) = 1.382, C(32)–C(33) = 1.518, C(25)–C(23)–N(3) = 128, C(32)–C(33)–N(5) = 112.



Employing an excess amount of the base (5 equiv.) in the reaction of $[\text{Cu-L1}]\text{PF}_6$ and phenylacetylene did not affect the mole ratio of the **Cu-A** and **Cu-S** drastically. However, it shifted the equilibrium toward the complete formation of the **Cu-S** and **Cu-A** species (Fig. 11). In addition, the deuteration of the methylene linkers in **Cu-A** and the methine linkers in **Cu-S** was accelerated. This was demonstrated by the significantly reduced intensity of these signals in the ^1H NMR spectrum of the reaction (Fig. S24b, SI), as well as the appearance of the methine linkers of **Cu-S** in the ^2H NMR spectrum (Fig. S25, SI). The absence of the methylene linkers of **Cu-A** from the ^2H NMR spectrum is attributed to the low concentration of this species in solution. These findings support the preference of **Cu-S** formation over **Cu-A** under both stoichiometric and non-stoichiometric conditions at room temperature. Interestingly, this pattern changed when a similar time-temperature profile was used to that in the catalytic carboxylation. Stirring a reaction mixture of copper, base, and alkyne for 12 hours at room temperature and 12 hours at 80 °C resulted in a significant drop in the amount of **Cu-S**. This was demonstrated by the 75 : 25 ratio of the $\text{CH}(\text{Pr})$ hydrogens for the $[\text{Cu-L1}]^+/\text{Cu-S}$ in the ^1H NMR spectrum (Fig. S26, SI). The absence of **Cu-A** signals, which are readily distinguished from those of $[\text{Cu-L1}]^+$ by the presence of the phenyl group in the aromatic region, is attributed to the species' instability at high temperatures, resulting in the formation of the starting complex and the acetylide anion (Fig. 9).

Reactivity of the Cu-CNC complexes with CO_2 in the presence of the base and phenylacetylene. To examine any potential reaction with CO_2 , the in situ-formed $[\text{Cu-L3}^*]$ complex was treated with CO_2 at atmospheric pressure in benzene. The rapid color change from dark red to orange, accompanied by



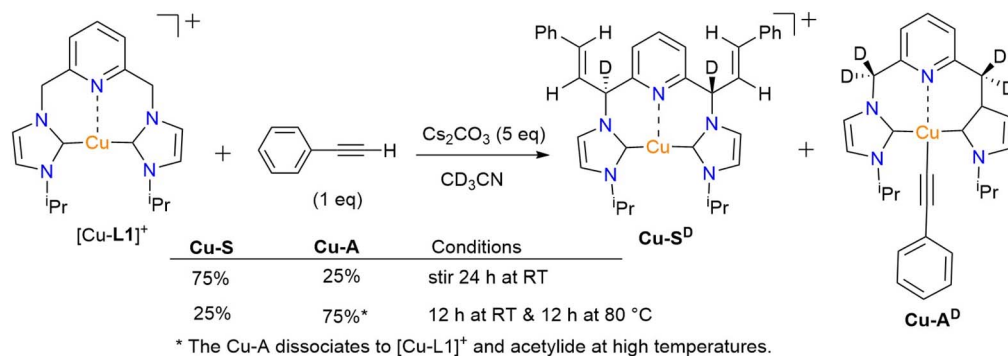


Fig. 11 Cu-acetylide (Cu-A^D) and Cu-styrene (Cu-S^D) complexes formed by reacting [Cu-L1]PF₆, phenylacetylene, and Cs₂O₃ in CD₃CN.

precipitation upon CO₂ exposure, indicates the formation of a new species. The ¹H NMR spectrum of the orange solid in CD₃CN after filtration and solvent removal under vacuum displays the characteristic peaks of the starting complex and a second set of resonance signals of much lower intensity (Fig. S27, SI). In the aromatic region of the spectrum, after masking the dominant peaks of the initial complex, seven notable resonance signals are observed. These signals are attributed to a complex featuring a carboxylate methylene (CHCO₂) linker. The complex's unsymmetrical nature is evident from the presence of seven aromatic peaks, rather than the five signals expected for a symmetrical dicarboxylate derivative. Additionally, the low-field singlet at 5.79 ppm is associated with the CHCO₂ linker and resembles a feature observed in the ¹H NMR spectrum of the rhodium analog.⁴¹ The lack of methylene signals for the other half of the [Cu-L3^{CO2}] complex and the diminished intensity of the CHCO₂ linker are likely due to deuteration (Fig. 4b). Furthermore, the significantly reduced intensities of the carboxylate complex resonances are attributed to the equilibrium nature of the reaction and its reversal upon solvent removal under vacuum (Fig. 12).

After examining the nucleophilic reactivity of the dearomatized Cu-CNC complex toward CO₂ and phenylacetylene individually, it would be insightful to investigate the reaction under simultaneous exposure to both reagents. To explore this concept, the in situ-formed Cu-S complex, obtained from the reaction of [Cu-L1]PF₆ with sodium acetylide (1 equiv.), was reacted with CO₂ (1 atm). The ¹H NMR spectrum of the reaction mixture revealed significantly different signals from those of the Cu-S^D and [Cu-L1]⁺ complexes (Fig. S28 and S29a, SI). The

pyridinic signals (*p*-Py δ(¹H) 7.75 ppm; *m*-Py δ(¹H) 7.37 ppm) have experienced an upfield shift compared to these signals of [Cu-L1]PF₆. Additionally, the aromatic resonances of the phenyl group have shifted upfield relative to the corresponding signals of the Cu-S^D and appear at a 2:2:1 integrated ratio of hydrogen. These signals also appear at a higher field (lower ppm) than those of the Cu-A^D complex (Fig. S29b, SI). The aromatic signals and the multiplet of the ¹Pr methine hydrogens at 4.83 ppm suggest the formation of a new species, likely a copper propiolate complex (Cu-Pr), in solution (Fig. 13). This assignment was further supported by the IR spectrum of the reaction in CD₃CN, which shows distinct absorption bands of C≡C stretching at $\bar{\nu}$ = 2662 cm⁻¹, asymmetric stretch of CO at $\bar{\nu}$ = 1602 cm⁻¹, and symmetric stretching of CO at $\bar{\nu}$ = 1331 cm⁻¹ (Fig. S30, SI). The more intense band of asymmetric stretching, compared to that of symmetric stretching, along with the significant frequency splitting of 271 cm⁻¹, suggests that the propiolate anion is likely coordinated to the metal instead of existing as a free propiolate ion.⁵⁹

It should be noted that the initially formed Cu-Pr complex is dearomatized, as is the case with Cu-S and Cu-A. This complex

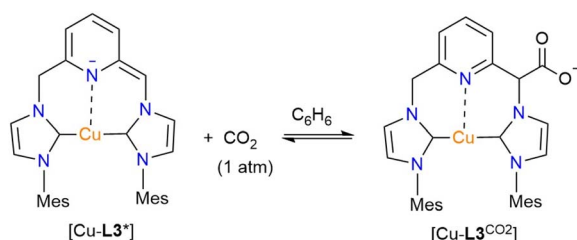


Fig. 12 The Cu-carboxylate complex formed in the reaction of [Cu-L3*] and CO₂ in benzene.

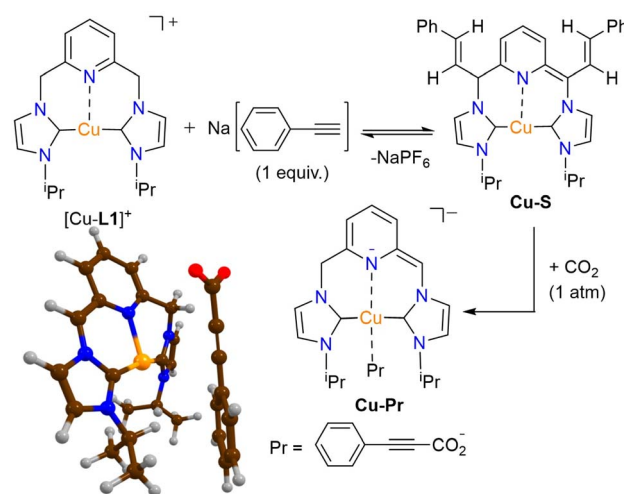


Fig. 13 The Cu-propiolate complex formed from the reaction of [Cu-L1]PF₆, NaPA, and CO₂ in CD₃CN, along with its DFT-optimized structure.




then undergoes deuterium exchange in CD_3CN , as indicated by the absence of its methylene hydrogens in the ^1H NMR spectrum (Fig. S28a, SI). Moreover, its formation is an equilibrium process that can be disrupted during a simple work-up to isolate the product. The ^1H NMR spectrum of the solid collected after removing acetonitrile under vacuum displays the dominant signals of the starting $[\text{Cu-L1}]\text{PF}_6$ and small amounts of protonated ligand (Fig. S31, SI). The same results were obtained when attempting to precipitate the **Cu-Pr** complex by adding a co-solvent to the reaction medium. The DFT-optimized structure of **Cu-Pr** is shown in Fig. 13 and is consistent with NMR spectroscopy findings in supporting the formation of the propiolate anion. However, the calculations showed the dissociated anion from copper in the gas phase as a lower-energy minimum in the optimization graph.

The formation of the **Cu-Pr** species from the reaction of **Cu-S** and CO_2 suggests the internal conversion of **Cu-S** to **Cu-A** in the presence of CO_2 (Fig. 13). While the mechanism of this transformation is yet to be understood, **Cu-A** complex is considered an essential intermediate in the carboxylation process due to its nucleophilic reactivity toward CO_2 . This was further verified by the reaction of the **Cu-A** complex with CO_2 . When the *in situ* formed **Cu-A**, produced by treating $[\text{Cu-L1}]\text{PF}_6$ with excess phenylacetylide, reacted with CO_2 , the NMR spectrum of the reaction (Fig. S32, SI) was nearly identical to that observed in the **Cu-S** reaction with CO_2 (Fig. S28a, SI). Furthermore, replacing phenylacetylene and Cs_2CO_3 with sodium phenylacetylide in the catalytic reaction yielded the propiolate ester product in 80% yield, thereby confirming the significance of the proposed intermediates in the carboxylation mechanism.

Proposed mechanism of direct carboxylation catalyzed by Cu-CNC complexes

Based on the experimental data described above, a possible mechanism for the Cu-CNC-catalyzed carboxylation of terminal alkynes with CO_2 is proposed (Scheme 3). The initial deprotonation of the methylene linker produces a highly reactive, dearomatized intermediate ($[\text{Cu-L}^*]$), which subsequently attacks phenylacetylene to form the styrene-functionalized **Cu-S** species. In the presence of CO_2 and at high temperatures, this species undergoes an internal conversion to the CNC-supported copper-acetylide (**Cu-A**) intermediate. Insertion of CO_2 into the Cu-C bond of **Cu-A** furnishes the copper-propiolate (**Cu-Pr**) in a reversible reaction. Further reaction of this species with alkyl halide regenerates the dearomatized complex and releases the propiolate ester product. It is worth noting that a subsequent reaction with solvent is a viable step for all the intermediates in the reaction cycle, including **Cu-S**, **Cu-A**, and **Cu-Pr**, as demonstrated by the ^1H NMR experiments in CD_3CN (*vide supra*). While this reaction results in the formation of saturated intermediates, the presence of excess Cs_2CO_3 ensures the steady regeneration of the dearomatized complexes and maintains their active form during the reaction.

After identifying the key intermediates in the mechanism, the mixed temperature profile of the carboxylation/esterification can be rationalized. While the formation of the

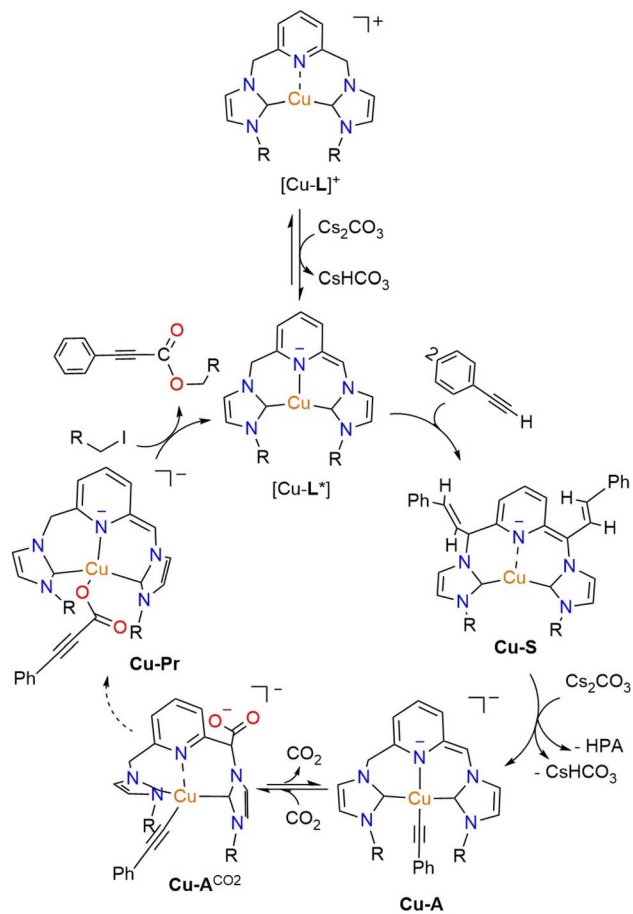

Scheme 3 A possible mechanism for the direct carboxylation of terminal alkynes by Cu-CNC through MLC. The specific states involved in the transition from **Cu-A** to **Cu-Pr** are unclear.

dearomatized complex, as the active form of the catalyst, is exothermic, the conversion of **Cu-S** to **Cu-A** and the esterification reaction occur more efficiently at higher temperatures. When the coupling of phenylpropionate salt and iodoethane was attempted in the absence of copper at room temperature, a minimal amount of ester (3%) was produced. The DFT calculations also confirmed the uphill nature of the **Cu-S** to **Cu-A** conversion and emphasized the necessity of elevated temperatures to facilitate the reaction toward **Cu-A** formation (Fig. S111, SI). Furthermore, the calculations supported a facile conversion of **Cu-A** to $[\text{Cu-L1}]^+$ and acetylide ion in the absence of CO_2 (Fig. S112, SI).

Conclusions

We have discovered a new set of Cu-CNC complexes for the tandem carboxylation and esterification of terminal alkynes using CO_2 , and have experimentally established its catalytic reaction mechanism. The catalyst's structure and reaction mechanism are notably distinct from those of previously reported copper complexes. In contrast to other Cu-NHC complexes, wherein the $[\text{Cu}(\text{NHC})(\text{OR})]$ ($\text{R} = \text{H}$, alkyl) is an active form of the catalyst, the Cu-CNC complexes perform



through an aromatization-dearomatization mechanism. We have also obtained the enthalpy and entropy of formation, as well as the activation parameters, of a dearomatized Cu-CNC complex. These findings represent the first report of thermodynamic and kinetic data for a dearomatized complex supported by lutidine-linked pincer ligands. Analyzing the individual steps of the mechanism by NMR spectroscopy revealed the *in situ* formation of three reactive intermediates in the carboxylation process: **Cu-S**, **Cu-A**, and **Cu-Pr**. The **Cu-S** species was formed *via* nucleophilic attack by the dearomatized complex on phenylacetylene, in a reaction similar to that observed for a Rh-CNC analog. The symmetrically substituted **Cu-S** species, with two styrene linkers, is distinct from its unsymmetrical Rh-CNC counterpart because it can internally convert to a copper-acetylide intermediate. The **Cu-A** species is a vital intermediate that can react with CO₂ and facilitates a subsequent carboxylation path. A similar reactivity and mechanism have not yet been documented with any other TM-CNC or carboxylation catalyst.

Author contributions

N. B. conducted most of the experiments, including synthesis, characterization, catalytic reactions, and mechanistic investigations, in collaboration with E. G. He also contributed to the manuscript's writing under the supervision of L. T., alongside written contributions and edits from the other authors. C. Z. performed all DFT calculations under the guidance of S. P. de V.

Conflicts of interest

The authors have no conflict of interest to declare.

Data availability

CCDC 2415955, 2415975, 2488390, 2494324 and 2514575 contain the supplementary crystallographic data for this paper.^{60a-c}

The data supporting this article are included in the supplementary information (SI). Supplementary information: synthetic procedures, structural characterizations (NMR spectra, mass data, X-ray data for [L3-Cu(PA)]₂ and elemental analysis), UV-Vis studies of rate and equilibrium constants at different temperatures, NMR studies of the reaction mechanism, DFT procedures and data, crystallographic information files (CIF) for [Cu-L3]PF₆, [Cu-L4]PF₆, [Cu-L3*], and [Cu-L1*], [L3-Cu(PA)]₂, and crystallographic data collection tables. See DOI: <https://doi.org/10.1039/d5sc08379f>.

Acknowledgements

LT thanks the Oklahoma Center for Advancement of Science and Technology, OCAST Health (HR23-008) program, and Iranian and Persian Gulf Studies (IPGS) program for financial support of this work. E. G. greatly acknowledges funding from the Lew Wentz Foundation. SdV thanks the Computational

Shared Facilities at the University of Manchester for CPU time provided.

References

- 1 K. A. Grice, Carbon dioxide reduction with homogenous early transition metal complexes: opportunities and challenges for developing CO₂ catalysis, *Coord. Chem. Rev.*, 2017, **336**, 78–95.
- 2 K. A. Grice and C. P. Kubiak, in *Adv. Inorg. Chem.*, ed. M. Aresta and R. van Eldik, Academic Press, 2014, vol. 66, pp. 163–188.
- 3 Y. Yamazaki, H. Takeda and O. Ishitani, Photocatalytic reduction of CO₂ using metal complexes, *J. Photochem. Photobiol., C*, 2015, **25**, 106–137.
- 4 A. J. Morris, G. J. Meyer and E. Fujita, Molecular approaches to the photocatalytic reduction of carbon dioxide for solar fuels, *Acc. Chem. Res.*, 2009, **42**, 1983–1994.
- 5 P.-Z. Li, X.-J. Wang, J. Liu, H. S. Phang, Y. Li and Y. Zhao, Highly effective carbon fixation via catalytic conversion of CO₂ by an acylamide-containing metal-organic framework, *Chem. Mater.*, 2017, **29**, 9256–9261.
- 6 H. He, J. A. Perman, G. Zhu and S. Ma, Metal-organic frameworks for CO₂ chemical transformations, *Small*, 2016, **12**, 6309–6324.
- 7 M. Lu, M. Zhang, J. Liu, Y. Chen, J. P. Liao, M. Y. Yang, Y. P. Cai, S. L. Li and Y. Q. Lan, Covalent organic framework based functional materials: Important catalysts for efficient CO₂ utilization, *Angew Chem. Int. Ed. Engl.*, 2022, **61**, e202200003.
- 8 R. Debek, F. Azzolina-Jury, A. Travert and F. Maugé, A review on plasma-catalytic methanation of carbon dioxide – Looking for an efficient catalyst, *Renewable Sustainable Energy Rev.*, 2019, **116**, 109427.
- 9 I. I. F. Boogaerts and S. P. Nolan, Carboxylation of C–H bonds using N-heterocyclic carbene gold(I) complexes, *J. Am. Chem. Soc.*, 2010, **132**, 8858–8859.
- 10 L. Zhang, J. Cheng, T. Ohishi and Z. Hou, Copper-catalyzed direct carboxylation of C-H bonds with carbon dioxide, *Angew. Chem., Int. Ed.*, 2010, **49**, 8670–8673.
- 11 I. I. F. Boogaerts, G. C. Fortman, M. R. L. Furst, C. S. J. Cazin and S. P. Nolan, Carboxylation of N-H/C-H bonds using N-heterocyclic carbene copper(I) complexes, *Angew. Chem., Int. Ed.*, 2010, **49**, 8674–8677.
- 12 M. Arndt, E. Risto, T. Krause and L. J. Goossen, C-H carboxylation of terminal alkynes catalyzed by low loadings of silver(I)/DMSO at ambient CO₂ pressure, *ChemCatChem*, 2012, **4**, 484–487.
- 13 D. Yu and Y. Zhang, Copper- and copper-N-heterocyclic carbene-catalyzed C–H activating carboxylation of terminal alkynes with CO₂ at ambient conditions, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 20184–20189.
- 14 X. Zhang, W.-Z. Zhang, X. Ren, L.-L. Zhang and X.-B. Lu, Ligand-free Ag(I)-catalyzed carboxylation of terminal alkynes with CO₂, *Org. Lett.*, 2011, **13**, 2402–2405.
- 15 D. Yu, M. X. Tan and Y. Zhang, Carboxylation of terminal alkynes with carbon dioxide catalyzed by poly(N-



- heterocyclic carbene)-supported silver nanoparticles, *Adv. Synth. Catal.*, 2012, **354**, 969–974.
- 16 Y. Fukue, S. Oi and Y. Inoue, Direct synthesis of alkyl 2-alkynoates from alk-1-yne, CO₂, and bromoalkanes catalysed by copper(I) or silver(I) salt, *J. Chem. Soc., Chem. Commun.*, 1994, 2091.
- 17 F. Lehmann, L. Lake, E. A. Currier, R. Olsson, U. Hacksell and K. Luthman, Design, parallel synthesis and SAR of novel urotensin II receptor agonists, *Eur. J. Med. Chem.*, 2007, **42**, 276–285.
- 18 D. M. D'Souza, A. Kiel, D.-P. Herten, F. Rominger and T. J. J. Müller, Synthesis, structure and emission properties of spirocyclic benzofuranones and dihydroindolones: a domino insertion–coupling–isomerization–Diels–Alder approach to rigid fluorophores, *Chem.–Eur. J.*, 2008, **14**, 529–547.
- 19 W. Jia and N. Jiao, Cu-catalyzed oxidative amidation of propiolic acids under air via decarboxylative coupling, *Org. Lett.*, 2010, **12**, 2000–2003.
- 20 Y. Dingyi and Z. Yugen, The direct carboxylation of terminal alkynes with carbon dioxide, *Green Chem.*, 2011, **13**, 1275–1279.
- 21 C. Jin, L. Zhang, E.-H. Xing, P.-F. Mu and E.-Q. Gao, Amides Enable Room-Temperature CO₂ Conversion: Simple Organic Molecules Challenging Metal Catalysts, *J. Org. Chem.*, 2025, **90**, 2521–2528.
- 22 L. Zhang, G. Li, E.-H. Xing, Y. Liu, C. Jin, Z. Du, Y. Xu, D. Zhang and E.-Q. Gao, Simple pyrazoles as efficient organocatalysts for alkyne–CO₂ carboxylation and one-pot construction of heterocycles, *Org. Chem. Front.*, 2024, **11**, 2062–2069.
- 23 L. Zhang and E.-Q. Gao, Catalytic C(sp)-H carboxylation with CO₂, *Coord. Chem. Rev.*, 2023, **486**, 215138.
- 24 J. Jover and F. Maseras, Computational characterization of the mechanism for coinage-metal-catalyzed carboxylation of terminal alkynes, *J. Org. Chem.*, 2014, **79**, 11981–11987.
- 25 L. J. Gooßen, N. Rodríguez, F. Manjolinho and P. P. Lange, Synthesis of propiolic acids via copper-catalyzed insertion of carbon dioxide into the C–H bond of terminal alkynes, *Adv. Synth. Catal.*, 2010, **352**, 2913–2917.
- 26 I. I. F. Boogaerts and S. P. Nolan, Direct C–H carboxylation with complexes of the coinage metals, *Chem. Commun.*, 2011, **47**, 3021–3024.
- 27 W.-Z. Zhang, W.-J. Li, X. Zhang, H. Zhou and X.-B. Lu, Cu(I)-catalyzed carboxylative coupling of terminal alkynes, allylic alcohols, and CO₂, *Org. Lett.*, 2010, **12**, 4748–4751.
- 28 K. Inamoto, N. Asano, K. Kobayashi, M. Yonemoto and Y. Kondo, A copper-based catalytic system for carboxylation of terminal alkynes: synthesis of alkyl 2-alkynoates, *Org. Biomol. Chem.*, 2012, **10**, 1514–1516.
- 29 R. Pradhan, K. L. Gutman, A. Mas Ud, E. B. Hulley and K. V. Waynant, Catalytic carboxylation of terminal alkynes with copper(I) azothioformamide complexes, *Organometallics*, 2023, **42**, 362–371.
- 30 F. G. Bordwell, G. E. Drucker, N. H. Andersen and A. D. Denniston, Acidities of hydrocarbons and sulfur-containing hydrocarbons in dimethyl sulfoxide solutions, *J. Am. Chem. Soc.*, 1986, **108**, 7310–7313.
- 31 L. Yang, Y. Yuan, H. Wang, N. Zhang and S. Hong, Theoretical insights into copper(I)-NHC-catalyzed C–H carboxylation of terminal alkynes with CO₂: the reaction mechanisms and the roles of NHC, *RSC Adv.*, 2014, **4**, 32457–32466.
- 32 D. Milstein, Discovery of environmentally benign catalytic reactions of alcohols catalyzed by pyridine-based pincer Ru complexes, based on metal–ligand cooperation, *Top. Catal.*, 2010, **53**, 915–923.
- 33 C. Gunanathan and D. Milstein, Metal–ligand cooperation by aromatization–dearomatization: a new paradigm in bond activation and “green” catalysis, *Acc. Chem. Res.*, 2011, **44**, 588–602.
- 34 T. Zell and D. Milstein, Hydrogenation and dehydrogenation iron pincer catalysts capable of metal–ligand cooperation by aromatization/dearomatization, *Acc. Chem. Res.*, 2015, **48**, 1979–1994.
- 35 F. Crisanti, M. Montag, D. Milstein, J. Bonin and N. von Wolff, Unlocking metal–ligand cooperative catalytic photochemical benzene carbonylation: a mechanistic approach, *Chem. Sci.*, 2024, **15**, 18052–18059.
- 36 J. I. van der Vlugt, E. A. Pidko, R. C. Bauer, Y. Gloaguen, M. K. Rong and M. Lutz, Dinuclear Copper(I) Thiolate Complexes with a Bridging Noninnocent PNP Ligand, *Chem.–Eur. J.*, 2011, **17**, 3850–3854.
- 37 J. I. van der Vlugt, E. A. Pidko, D. Vogt, M. Lutz and A. L. Spek, CuI Complexes with a Noninnocent PNP Ligand: Selective Dearomatization and Electrophilic Addition Reactivity, *Inorg. Chem.*, 2009, **48**, 7513–7515.
- 38 M. Hernández-Juárez, M. Vaquero, E. Álvarez, V. Salazar and A. Suárez, Hydrogenation of imines catalysed by ruthenium(II) complexes based on lutidine-derived CNC pincer ligands, *Dalton Trans.*, 2013, **42**, 351–354.
- 39 G. A. Filonenko, E. Cosimi, L. Lefort, M. P. Conley, C. Copéret, M. Lutz, E. J. M. Hensen and E. A. Pidko, Lutidine-derived Ru-CNC hydrogenation pincer catalysts with versatile coordination properties, *ACS Catal.*, 2014, **4**, 2667–2671.
- 40 P. Hermosilla, P. García-Orduña, F. J. Lahoz, V. Polo and M. A. Casado, Rh complexes with pincer carbene CNC lutidine-based ligands: reactivity studies toward H₂ addition, *Organometallics*, 2021, **40**, 3720–3732.
- 41 P. Hermosilla, P. García-Orduña, P. J. Sanz Miguel, V. Polo and M. A. Casado, Nucleophilic reactivity at a =CH arm of a lutidine-based CNC/Rh system: Unusual alkyne and CO₂ activation, *Inorg. Chem.*, 2022, **61**, 7120–7129.
- 42 D. Domyati, S. L. Hope, R. Latifi, M. D. Hearn and L. Tahsini, Cu(I) complexes of pincer pyridine-based N-heterocyclic carbenes with small wingtip substituents: synthesis and structural and spectroscopic studies, *Inorg. Chem.*, 2016, **55**, 11685–11693.
- 43 J. L. Minnick, J. Raincrow, G. Meinders, R. Latifi and L. Tahsini, Synthesis, characterization, and spectroscopic studies of 2,6-dimethylpyridyl-linked Cu(I)-CNC



- complexes: The electronic influence of aryl wingtips on copper centers, *Inorg. Chem.*, 2023, **62**, 15912–15926.
- 44 R. E. Andrew and A. B. Chaplin, Synthesis and reactivity of NHC-based rhodium macrocycles, *Inorg. Chem.*, 2015, **54**, 312–322.
- 45 J. Bermejo, L. L. Santos, E. Álvarez, J. López-Serrano and A. Suárez, Oxidation of alcohols to carboxylates with N₂O catalyzed by ruthenium(II)-CNC complexes, *ACS Catal.*, 2025, **15**, 11530–11543.
- 46 J. L. Minnick, D. Domyati, R. Ammons and L. Tahsini, C–X (X = N, O) cross-coupling reactions catalyzed by copper-pincer bis(N-heterocyclic carbene) complexes, *Front. Chem.*, 2019, **7**(12), 1–9.
- 47 D. Domyati, R. Latifi and L. Tahsini, Sonogashira-type cross-coupling reactions catalyzed by copper complexes of pincer N-heterocyclic carbenes, *J. Organomet. Chem.*, 2018, **860**, 98–105.
- 48 E. Raamat, K. Kaupmees, G. Ovsjannikov, A. Trummal, A. Kütt, J. Saame, I. Koppel, I. Kaljurand, L. Lipping, T. Rodima, V. Pihl, I. A. Koppel and I. Leito, Acidities of strong neutral Brønsted acids in different media, *J. Phys. Org. Chem.*, 2013, **26**, 162–170.
- 49 E. J. Park, S. H. Kim and S. Chang, Copper-catalyzed reaction of α -aryldiazoesters with terminal alkynes: a formal [3 + 2] cycloaddition route leading to indene derivatives, *J. Am. Chem. Soc.*, 2008, **130**, 17268–17269.
- 50 B. Yu, Z.-F. Diao, C.-X. Guo, C.-L. Zhong, L.-N. He, Y.-N. Zhao, Q.-W. Song, A.-H. Liu and J.-Q. Wang, Carboxylation of terminal alkynes at ambient CO₂ pressure in ethylene carbonate, *Green Chem.*, 2013, **15**, 2401–2407.
- 51 Y. Song, Y. Zhang, Z. Chen and X.-F. Wu, Recent advances in copper-catalyzed carboxylation reactions with CO₂, *Asian J. Org. Chem.*, 2022, **11**, e202200237.
- 52 G. C. Fortman, A. M. Z. Slawin and S. P. Nolan, A versatile cuprous synthon: [Cu(IPr)(OH)] (IPr = 1,3-bis(diisopropylphenyl)imidazol-2-ylidene), *Organometallics*, 2010, **29**, 3966–3972.
- 53 R. Yuan and Z. Lin, Mechanism for the carboxylative coupling reaction of a terminal alkyne, CO₂, and an allylic chloride catalyzed by the Cu(I) complex: a DFT study, *ACS Catal.*, 2014, **4**, 4466–4473.
- 54 K. N. Houk and N. G. Rondan, Origin of negative activation energies and entropy control of halocarbene cycloadditions and related fast reactions, *J. Am. Chem. Soc.*, 1984, **106**, 4293–4294.
- 55 R. A. Moss, W. Lawrynowicz, N. J. Turro, I. R. Gould and Y. Cha, Activation parameters for the additions of arylhalocarbenes to alkenes, *J. Am. Chem. Soc.*, 1986, **108**, 7028–7032.
- 56 N. Back, C. D. Hunt and L. Tahsini, unpublished work.
- 57 L. A. Goj, E. D. Blue, C. Munro-Leighton, T. B. Gunnoe and J. L. Petersen, Cleavage of X–H bonds (X = N, O, or C) by copper(I) alkyl complexes to form monomeric two-coordinate copper(I) systems, *Inorg. Chem.*, 2005, **44**, 8647–8649.
- 58 D. Yu, S. P. Teong and Y. Zhang, Transition metal complex catalyzed carboxylation reactions with CO₂, *Coord. Chem. Rev.*, 2015, **293–294**, 279–291.
- 59 E. G. Palacios, G. Juárez-López and A. J. Monhemius, Infrared spectroscopy of metal carboxylates: II. Analysis of Fe(III), Ni and Zn carboxylate solutions, *Hydrometallurgy*, 2004, **72**, 139–148.
- 60 (a) CCDC 2415955: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2m301t](https://doi.org/10.5517/ccdc.csd.cc2m301t); (b) CCDC 2415975: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2m30pg](https://doi.org/10.5517/ccdc.csd.cc2m30pg); (c) CCDC 2488390: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2pjcn8](https://doi.org/10.5517/ccdc.csd.cc2pjcn8); (d) CCDC 2494324: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2pqk22](https://doi.org/10.5517/ccdc.csd.cc2pqk22); (e) CCDC 2514575: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2qdm3](https://doi.org/10.5517/ccdc.csd.cc2qdm3).

